



HAL
open science

Internal states of model isotropic granular packings. III. Elastic properties.

Ivana Agnolin, Jean-Noël Roux

► **To cite this version:**

Ivana Agnolin, Jean-Noël Roux. Internal states of model isotropic granular packings. III. Elastic properties.. 2006. hal-00148554v1

HAL Id: hal-00148554

<https://hal.science/hal-00148554v1>

Preprint submitted on 22 May 2007 (v1), last revised 18 Dec 2007 (v4)

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Internal states of model isotropic granular packings.

III. Elastic properties.

Ivana Agnolin and Jean-Noël Roux*

Laboratoire des Matériaux et des Structures du Génie Civil[†], Institut Navier,
2 allée Kepler, Cité Descartes, 77420 Champs-sur-Marne, France

(Dated: May 22, 2007)

In this third and final paper of a series, elastic properties of numerically simulated isotropic packings of spherical beads assembled by different procedures [1] and subjected to a varying confining pressure [2] are investigated. In addition to the pressure, which determines the stiffness of contacts because of Hertz's law, elastic moduli are chiefly sensitive to the coordination number, the possible values of which between different microstructures are not necessarily correlated with the density. Comparisons of numerical and experimental results for glass beads in the 10kPa – 10MPa pressure range reveal similar differences between dry samples prepared in a dense state by vibrations and lubricated packings, so that the greater stiffness of the latter, in spite of their lower density, can be attributed to a larger coordination number. Effective medium type approaches, or Voigt and Reuss bounds, provide good estimates of bulk modulus B , which can be accurately bracketed, but badly fail for shear modulus G , especially in low z^* configurations under low pressure. This is due to the different response of tenuous, fragile networks to changes in load *direction*, as compared to load *intensity*. The shear modulus normalized by the average contact stiffness, in poorly coordinated packings, tends to vary proportionally to the degree of force indeterminacy per unit volume, although, unlike in the frictionless case, the level of hyperstaticity does not appear to vanish in the rigid limit. The elastic range extends to small strain intervals and compares well with experimental observations on sands. The origins of nonelastic response are discussed. We conclude that elastic moduli provide access to mechanically important information about coordination numbers, which escape direct measurement techniques, and indicate further perspectives.

PACS numbers: 45.70.-n, 83.80.Fg, 46.65.+g, 62.20.Fe

I. INTRODUCTION

The mechanical properties of granular materials and their relations to the packing microstructure are currently being investigated by many research groups. As a simple model, long studied for its geometric aspects [3, 4], the packing of equal-sized spherical balls is also mechanically characterized in the laboratory [5, 6, 7, 8, 9], and by numerical means, relying on discrete, granular level modeling [8, 10, 11, 12, 13, 14].

The present paper is the last one in a series of three, about geometric and mechanical properties of bead packings obtained by numerical simulations. It focusses on elastic properties of isotropically compressed samples. The study is based on the configurations for which the packing processes and resulting microstructure were studied in paper I [1], while paper II [2] reported on the effects of isotropic compressions and pressure cycles.

Elastic properties of granular assemblies are probed when small stress increments are superimposed on a pre-stressed equilibrium configuration, either on controlling very small strains in a static experiment [6, 15, 16, 17] or in dynamical ones, relying on resonance modes [18, 19,

20], or sound propagation [6, 7, 15, 17, 20, 21, 22, 23, 24]. Elastic behavior of granular materials is only applicable for very small strain increments, typically of order 10^{-5} or even 10^{-6} in usual conditions, *i.e.*, with sands under confining stresses between 10 kPa and a few MPa [6, 15, 16, 17]. It has been checked in such cases that static measurements of elastic moduli, with devices accurate enough to control such small strains are consistent with “dynamical” ones, *i.e.* deduced from experiments on wave propagation or resonance frequencies. Experimental soil mechanics have achieved a high level of sophistication, with significant progress over the last twenty years [25, 26], and accurate measurements of the mechanical response of granular materials in the very small strain régime are one example thereof. Coincidence of elastic moduli values obtained by different means is reported, *e.g.*, in [15, 17, 20]. Such moduli should not be confused with the slope of stress-strain curves on the scale of the strain level (usually in the 1% range) corresponding to the full mobilization of internal friction. Such slopes are considerably smaller than true elastic moduli (by more than an order of magnitude), and do not correspond to an elastic, reversible response. In this respect, the frequent use, for practical engineering purposes, of a simplified linear elastic behavior supplemented with the Mohr-Coulomb criterion for plasticity and an appropriately dilatant flow rule, as presented in Ref. [27], should not be misinterpreted. Such crude models, in which strains are elastic and reversible up to the maximum deviator stress (full internal friction mobiliza-

[†]LMSGC is a joint laboratory depending on Laboratoire Central des Ponts et Chaussées, École Nationale des Ponts et Chaussées and Centre National de la Recherche Scientifique

*Electronic address: jean-noel.roux@lcpc.fr

tion), are resorted to in engineering practice when detailed information on the constitutive law of the material are not available, but the “elastic moduli” introduced in those caricatured constitutive relations are merely convenient parameters enabling one to perform approximate calculations.

In micromechanical [28, 29] and numerical [8, 12, 30] studies, elastic properties are associated with the deformations of a fixed contact network, and should therefore correspond to the “true elastic” behavior observed in the laboratory for very small strain intervals. Indeed, except in very special situations in which the effects of friction are suppressed and geometric restructuring is reversible [31, 32], the irreversible changes associated with network alterations or rearrangements preclude all kind of elastic modelling. Elastic properties are therefore attached to one specific contact set, as explained in Section II C. Consequently, they are of limited relevance to the global mechanical behavior and the rheology of granular materials. Nevertheless, elastic properties are interesting because they might provide access, in a non-destructive way, to geometric data on the contact network, such as coordination numbers. Such variables are still virtually inaccessible to direct measurements, even with sophisticated visualization techniques, as emphasized in paper I [1], but they are very likely, in turn, to influence the rheological constitutive laws for larger strains.

This paper is organized in the following way. We first recall the properties of the model material we are studying (Section II), along with basic definitions and properties pertaining to the elasticity of granular packings. Then, useful results on the pressure-dependent internal states of the various types of configurations introduced and studied in papers I and II [1, 2] are summarized in Section III. Next, the values of elastic constants in the different configuration series, as a function of (isotropic) confining pressure, are presented in Section IV, where their relations to internal structure are also discussed. Section V is devoted to the particular behavior of elastic moduli in the tenuous contact networks of poorly coordinated configurations. Numerical results are confronted to experimental ones in Section VI. Some results about the extension of the elastic range are given in Section VII. Section VIII discusses the results and indicates some further perspectives.

II. NUMERICAL MODEL AND BASIC DEFINITIONS

Packings of spherical beads are simulated with molecular dynamics, in which equations of motions resulting from Newton’s laws are solved for the particle positions and rotations. Thanks to a suitably adapted form of the Parrinello-Rahman deformable cell molecular dynamics technique [33, 34], as described in paper I [1], we request all three diagonal components of the Cauchy stress ten-

sor, denoted as usual as $\sigma_{\alpha\alpha}$ to be equal, in equilibrium, to prescribed values $\Sigma_{\alpha\alpha}$, all chosen to coincide with a pressure P in this study of isotropic states. Differences between $\sigma_{\alpha\alpha}$ and $\Sigma_{\alpha\alpha}$ entail some evolution in the cell size parameters. $\sigma_{\alpha\alpha}$ is given in equilibrium by the classical formula:

$$\sigma_{\alpha\alpha} = \frac{1}{\Omega} \sum_{i < j} F_{ij}^{(\alpha)} r_{ij}^{(\alpha)}, \quad (1)$$

where the sum runs over all pairs in contact, $F_{ij}^{(\alpha)}$ is the α coordinate of the force \mathbf{T}_{ij} exerted by grain i onto its neighbor j at their contact, while $r_{ij}^{(\alpha)}$ is the α coordinate of vector \mathbf{r}_{ij} , pointing from the center of i to the center of j . From Eqn. (1) one can easily deduce a simple and useful relation between pressure $P = (\sigma_{11} + \sigma_{22} + \sigma_{33})/3$ and the average normal contact force $\langle N \rangle$ between mono-sized spheres of diameter a , involving solid fraction Φ and coordination number z :

$$P = \frac{z\Phi\langle N \rangle}{\pi a^2}, \quad (2)$$

The corresponding dynamical equations used to impose stresses are described in paper I [1], and we briefly recall here the essential ingredients of the model for a study of the elastic response of packings that have been first assembled and compressed, as reported in papers I and II. *Dynamical* aspects of the model, in particular (inertia, viscous dissipation) play no role in the determination of elastic moduli, for which our calculations are based on the building of the *stiffness matrix* of the contact network.

A. Local stiffnesses

We consider spherical beads of diameter a , with the elastic properties of glass: Young modulus $E = 70$ GPa, Poisson ratio $\nu = 0.3$. They interact in their contacts by the Hertz law, which states that the elastic normal force N is proportional to $h^{3/2}$, h being the normal deflection of the contact, so that the incremental normal stiffness $\frac{dN}{dh}$, with the notation $\tilde{E} = \frac{E}{1-\nu^2}$, is given by:

$$K_N = \frac{dN}{dh} = \frac{\tilde{E}\sqrt{a}}{2} h^{1/2} = \frac{3^{1/3}}{2} \tilde{E}^{2/3} a^{1/3} N^{1/3} \quad (3)$$

The tangential elastic force is to be incrementally evaluated with a simplified Mindlin-Deresiewicz form [35] on assuming the tangential stiffness K_T to stay proportional to K_N , and hence a function of N :

$$K_T = \frac{2-2\nu}{2-\nu} K_N \quad (4)$$

The tangential force \mathbf{T} is constrained by the Coulomb condition $\|\mathbf{T}\| \leq \mu N$, with friction coefficient μ set to 0.3, and additional conditions are introduced to ensure thermodynamic consistency and objectivity (see paper I [1, Sec. II, appendices A and B]).

All our results will be stated in a form independent of bead diameter a . All dimensionless results – such as *e.g.* ratios of elastic moduli of the granular material to \tilde{E} – depend, in addition to ν , on a reduced stiffness parameter we define as

$$\kappa = \left(\frac{\tilde{E}}{P} \right)^{2/3}.$$

Typical values of contact deflections h scale as $\kappa^{-1}a$.

Let N_c denote the number of force-carrying contacts. In every contacting pair i - j , we arbitrarily choose a “first” grain i and a “second” one j , and define the relative displacement vector $\delta\mathbf{u}_{ij}$ as the difference between the displacement of the contact point as belonging to solid i and its displacement as a point belonging to solid j , both regarded as rigid.

In each contact the force \mathbf{F}_{ij} that is transmitted from i to j is split into its normal and tangential components as $\mathbf{F}_{ij} = N_{ij}\mathbf{n}_{ij} + \mathbf{T}_{ij}$. The static contact law relates the $3N_c$ -dimensional contact force increment vector $\Delta\mathbf{f}$, formed with the values ΔN_{ij} , $\Delta\mathbf{T}_{ij}$ of the normal and tangential parts of all contact force increments, to $\delta\mathbf{u}$:

$$\Delta\mathbf{f} = \underline{\underline{\mathcal{K}}} \cdot \delta\mathbf{u}. \quad (5)$$

This defines the $(3N_c \times 3N_c)$ matrix of contact stiffnesses $\underline{\underline{\mathcal{K}}}$. $\underline{\underline{\mathcal{K}}}$ is block diagonal (it does not couple different contacts), and we shall refer to it as the *local stiffness matrix*. The $3 \times d$ block of $\underline{\underline{\mathcal{K}}}$ corresponding to contact i, j , $\underline{\underline{\mathcal{K}}}_{ij}$ is diagonal itself provided friction is not fully mobilized, and contains stiffnesses $K_N(h_{ij})$ and (twice in 3 dimensions) $K_T(h_{ij})$ as given by (3) and (4):

$$\underline{\underline{\mathcal{K}}}_{ij}^E = \begin{bmatrix} K_N(h_{ij}) & 0 & 0 \\ 0 & K_T(h_{ij}) & 0 \\ 0 & 0 & K_T(h_{ij}) \end{bmatrix} \quad (6)$$

This simple form of $\underline{\underline{\mathcal{K}}}_{ij}$ ignores some non-diagonal terms that appear when the normal force decreases, or for sliding contacts. Such terms are discussed below and in Appendix A, and will be shown to be negligible in the context of the study of elastic properties of bead packings.

B. Global rigidity and stiffness matrices

When elastic properties are investigated, small displacements about an equilibrium configurations are dealt with to first order (as an infinitesimal motion, *i.e.* just like velocities), and related to small increments of applied forces, moments and stresses. We use periodic boundary conditions in our simulations, and the dimensions L_α ($\alpha = 1, 2, 3$) of the parallelepipedic simulation cell are part of the degrees of freedom of the system, while all three diagonal components of the stress tensor are externally imposed [1, 2]. We use three strain parameters defined as the relative changes of those lengths, from

their values in a reference state:

$$\epsilon_\alpha = -\Delta L_\alpha / L_\alpha$$

Shrinking strains are positive.

Let us now recall the definition of the *rigidity matrix* (not to be confused with the stiffness matrix), as introduced in paper I. The grain center displacements $(\mathbf{u}_i)_{1 \leq i \leq n}$ are conveniently written as

$$\mathbf{u}_i = \tilde{\mathbf{u}}_i - \underline{\underline{\epsilon}} \cdot \mathbf{r}_i,$$

with a set of displacements $\tilde{\mathbf{u}}_i$ satisfying periodic boundary conditions in the cell with the current dimensions, $\underline{\underline{\epsilon}}$ denoting the diagonal strain matrix with coefficients ϵ_α . Gathering all coordinates of particle (periodic) displacements and rotation increments, and strain parameters one defines a *displacement vector* in a space with dimension equal to the number of degrees of freedom $N_f = 3n + 3$,

$$\mathbf{U} = ((\tilde{\mathbf{u}}_i, \Delta\theta_i)_{1 \leq i \leq n}, (\epsilon_\alpha)_{1 \leq \alpha \leq d}). \quad (7)$$

The normal unit vector \mathbf{n}_{ij} points from i to j (along the line joining centers for spheres). The relative displacement $\delta\mathbf{u}_{ij}$, for spherical grains with radius R , reads

$$\delta\mathbf{u}_{ij} = \tilde{\mathbf{u}}_i + \delta\theta_i \times R\mathbf{n}_{ij} - \tilde{\mathbf{u}}_j + \delta\theta_j \times R\mathbf{n}_{ij} + \underline{\underline{\epsilon}} \cdot \mathbf{r}_{ij}, \quad (8)$$

in which \mathbf{r}_{ij} is the vector pointing from the center of the first sphere i to the nearest image (by the periodic translation group of the boundary conditions) of the center of the second one j . The normal part $\delta\mathbf{u}_{ij}^N$ of $\delta\mathbf{u}_{ij}$ is the increment of normal deflection h_{ij} in the contact.

The rigidity matrix $\underline{\underline{\mathbf{G}}}$ is $3N_c \times N_f$ -dimensional, it is defined by the linear correspondence expressed by relation (8), which transforms \mathbf{U} into the $3N_c$ -dimensional vector of relative displacements at contacts $\delta\mathbf{u}$:

$$\delta\mathbf{u} = \underline{\underline{\mathbf{G}}} \cdot \mathbf{U} \quad (9)$$

External forces \mathbf{F}_i and moments $\mathbf{\Gamma}_i$ (at the center) applied to the grains, and diagonal Cauchy stress components Σ_α can be gathered in one N_f -dimensional *load vector* \mathbf{F}^{ext} :

$$\mathbf{F}^{\text{ext}} = ((\mathbf{F}_i, \mathbf{\Gamma}_i)_{1 \leq i \leq n}, (\Omega\Sigma_\alpha)_{1 \leq \alpha \leq d}), \quad (10)$$

chosen such that the work in a small motion is equal to $\mathbf{F}^{\text{ext}} \cdot \mathbf{U}$. The equilibrium equations – the statements that contact forces \mathbf{f} balance load \mathbf{F}^{ext} – is simply written with the transposed rigidity matrix, as

$$\mathbf{F}^{\text{ext}} = \mathbf{T}\underline{\underline{\mathbf{G}}} \cdot \mathbf{f}. \quad (11)$$

This is of course easily checked on writing down all force and moment coordinates, as well as the equilibrium form of stresses:

$$\Omega\Sigma_\alpha = \sum_{i < j} F_{ij}^\alpha r_{ij}^\alpha. \quad (12)$$

Given (9), (11) is equivalent to the theorem of virtual work, as stated in paper I [1].

Returning to the case of small displacements associated with a load increment $\Delta \mathbf{F}^{\text{ext}}$, one may write, to first order in \mathbf{U} ,

$$\Delta \mathbf{F}^{\text{ext}} = \underline{\underline{\mathbf{K}}} \cdot \mathbf{U}, \quad (13)$$

with a *total stiffness matrix* $\underline{\underline{\mathbf{K}}}$, comprising two parts, $\underline{\underline{\mathbf{K}}}^{(1)}$ and $\underline{\underline{\mathbf{K}}}^{(2)}$, which we respectively refer to as the *constitutive* and *geometric* stiffness matrices. $\underline{\underline{\mathbf{K}}}^{(1)}$ results from Eqns. 9, 5 and 11

$$\underline{\underline{\mathbf{K}}}^{(1)} = \mathbf{T} \underline{\underline{\mathbf{G}}} \cdot \underline{\underline{\mathcal{K}}} \cdot \underline{\underline{\mathbf{G}}} \quad (14)$$

$\underline{\underline{\mathbf{K}}}^{(2)}$ is due to the change of the geometry of the packing, and is written down in Appendix B, where it is also shown to be negligible in general.

To the rigidity matrix are associated the concepts of force and velocity (or displacement) indeterminacy, of relative displacement compatibility and of static admissibility of contact forces. Those definitions are given in paper I, where they are used to discuss the limit of iso-static packings [32].

C. Grain-level and macroscopic elasticity

We now come to a discussion of the conditions for which the response to load increments of a prestressed granular packing in mechanical equilibrium can be described as elastic, and explain how macroscopic elastic moduli are computed in our simulations.

Elasticity implies the existence of an elastic potential, function of displacements, from which forces are derived. If force increments are written as linearly depending on displacements, as in (13), the corresponding stiffness matrix $\underline{\underline{\mathbf{K}}}$ should be unique (the same for all \mathbf{U} vectors) and symmetric. In the preceding sections, some contributions to stiffness matrix $\underline{\underline{\mathbf{K}}}$ were found non-symmetric and dependent on the direction of displacements. This excludes a strictly elastic response. However, it turns out that non-symmetric and direction-dependent terms can be neglected in practice, for reasons recalled or stated below. It is consequently a good approximation to model the response to small load increment as elastic.

First, the effect on tangential contact force \mathbf{T} of a reduction of normal deflection h in a contact changes the symmetric form $\underline{\underline{\mathcal{K}}}_{ij}^E$ given in (6) into $\underline{\underline{\mathcal{K}}}_{ij}^R$, as written in Appendix A (Eqn. A1). We checked (see Appendix A) that its influence on elastic moduli is negligible in the isotropic samples we studied.

Full mobilization of friction also leads to a non-symmetric form of $\underline{\underline{\mathcal{K}}}$, which depends on the direction of displacements (see Eqn (A4) in Appendix A). However, it is always observed in the practice of MD simulations that once an equilibrium configuration is reached, the Coulomb criterion is satisfied as a strict inequality

in all contacts. The stiffness matrix is therefore to be built with the symmetric block of formula (6). One may object of course that we simplified the Hertz-Mindlin contact laws. More sophisticated models do not treat stiffness ratio K_T/K_N as a constant, and involve directional dependence (and slip in part of the contact region) before $\|\mathbf{T}\|$ reaches its maximum value μN . The possible effects of such more accurate contact laws on the apparent, macroscopic elastic properties are also assessed in Appendix A, and shown to be very weak.

Finally, the non-symmetric geometric contribution $\underline{\underline{\mathbf{K}}}^{(2)}$ (Appendix B) should be negligible, except of course when applied to displacements vectors \mathbf{U} within the kernel of the constitutive matrix $\underline{\underline{\mathbf{K}}}^{(1)}$. On using the symmetric diagonal form (6) for all contacts, $\underline{\underline{\mathbf{K}}}$ will be symmetric and positive definite. Consequently, in view of (14), the kernel of $\underline{\underline{\mathbf{K}}}^{(1)}$ (the ‘‘floppy modes’’ of the constitutive stiffness matrix) coincides with the kernel of $\underline{\underline{\mathbf{G}}}$ (the ‘‘mechanisms’’). If non-trivial mechanisms are present, one should investigate, for a prestressed system, the effects of the geometric stiffness matrix $\underline{\underline{\mathbf{K}}}^{(2)}$ (see Appendix B). We checked in paper I [1] that bead packings in equilibrium under prescribed stresses only possess localized, harmless mechanisms, in the sense that they do not jeopardize global stability. Such floppy modes can safely be eliminated, just like the global rigid-body motions.

To summarize, we shall neglect the geometric stiffness matrix $\underline{\underline{\mathbf{K}}}^{(2)}$, and approximate, within the constitutive one, the contact stiffness matrix $\underline{\underline{\mathcal{K}}}$ by its symmetric elastic form, given by (6). In order to evaluate macroscopic elastic moduli or compliances, one can apply stress increments and measure the resulting strains. With our choice of boundary conditions and degrees of freedom, we choose load increments $\Delta \mathbf{F}^{\text{ext}}$ with all coordinates set to zero except one of the three last ones, say $\Omega \Delta \sigma_{\alpha\alpha}$ corresponding to a diagonal stress increment, according to definition (10). Then we solve the system of equations (13) for the unknown displacement vector \mathbf{U} . Its 3 last coordinates are identified as diagonal strain components, according to definition (7). The effective elastic properties of the packing being isotropic, we obtain $\epsilon_\alpha = \sigma_\alpha / E^*$, and $\epsilon_\beta = -\nu^* \sigma_\alpha / E^*$ for $\beta \neq \alpha$, in which E^* and ν^* are the effective macroscopic Young modulus and Poisson coefficient of the bead packing. On changing α , and of course on using different samples, one obtains different estimates of those macroscopic properties, which should coincide in the limit of large systems.

In order to write down bounds on macroscopic elastic moduli, the following *minimization properties* are useful [36]. First, solving (13) for \mathbf{U} is equivalent to minimizing the following potential energy:

$$W_1(\mathbf{U}) = \frac{1}{2} \mathbf{U} \cdot \underline{\underline{\mathbf{K}}} \cdot \mathbf{U} - \Delta \mathbf{F}^{\text{ext}} \cdot \mathbf{U}. \quad (15)$$

Then, the contact force vector increment $\Delta \mathbf{f}$ minimizes

$$W_2(\Delta \mathbf{f}) = \frac{1}{2} \Delta \mathbf{f} \cdot \underline{\underline{\mathcal{K}}}^{-1} \Delta \mathbf{f}, \quad (16)$$

subject to the constraint that it should be statically admissible with load increment $\Delta \mathbf{F}^{\text{ext}}$. Minimal values in (15) and (16) are opposite to each other, and are identified in the limit of large systems with the corresponding macroscopic elastic energy, *i.e.*

$$\mp \frac{\Omega}{2} \underline{\underline{\underline{\underline{\epsilon}}}} : \underline{\underline{\underline{\underline{C}}}} : \underline{\underline{\underline{\underline{\epsilon}}}} = \mp \frac{\Omega}{2} \underline{\underline{\underline{\underline{\Delta\sigma}}}} : \underline{\underline{\underline{\underline{C}}}}^{-1} : \underline{\underline{\underline{\underline{\Delta\sigma}}}},$$

in which $\underline{\underline{\underline{\underline{C}}}}$ denotes the 4th rank tensor of elastic moduli. Those variational properties are directly analogous to classical result in elasticity of heterogeneous continua [37], and will be used in Section IV (technical details being supplied in Appendix D).

Finally, as explained in Appendix C, there are some small corrections to elastic moduli due to the effect of stresses in the configuration to which load increments are applied, of the order of the equilibrium pressure, and therefore negligible.


III. SAMPLE PREPARATION AND COMPRESSION

We summarize here the information about configurations assembled by different methods, as studied in paper I [1], and then isotropically compressed to various level of pressure, as reported in paper II [2].


Four different configuration series which, as in papers I and II, we keep referring to as A to D, were prepared under a rather low pressure ($\kappa = 39000$, corresponding to 10 kPa for glass beads, or $\kappa = 181000$, corresponding to 1 kPa), and then quasistatically compressed up to 100 MPa ($\kappa \simeq 80$), with friction coefficient $\mu = 0.3$ in the contacts.

They are characterized in terms of solid fraction Φ , coordination number z (average number of force-carrying contacts per grain), proportion of *rattlers* x_0 (those grains do not participate in force transmission at equilibrium), normal force distribution, friction mobilization, and geometric data such as distribution of interneighbor gaps and some local order parameters.


Configurations A, B and D were assembled on compressing a granular gas. Configurations C are obtained from A and are supposed to mimic, in a simplified way, the dense states obtained by vibration. Type A samples are assembled without friction, and correspond to the ideal “random close packing” state, which according to the available numerical evidence is uniquely defined, provided the compaction process is fast enough to avoid all incipient crystalline order nucleation [1, Section III]. Their solid fraction, accordingly, is slightly below 0.64 at low pressure, while the coordination number is close to 6, with few rattlers. Type A configurations may thus be regarded as a simple model for grains that are perfectly lubricated in the assembling stage, but such that dry intergranular contacts have a frictional behavior ($\mu = 0.3$) in quasistatic compression. As a variant, another set of samples was prepared on compressing without friction,

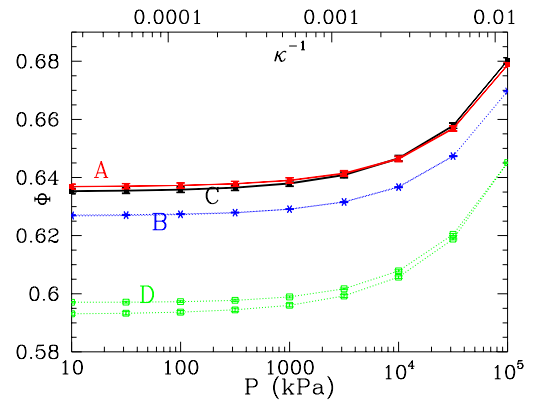

(a) Φ versus P or κ^{-1}

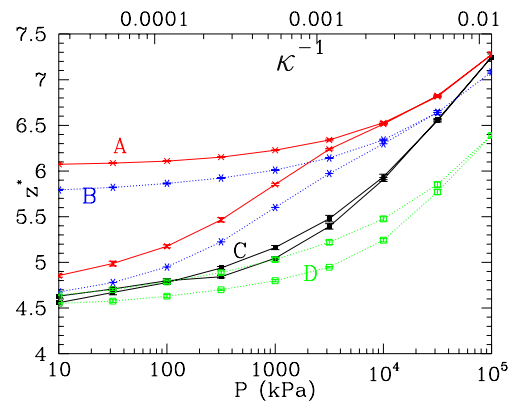

(b) z^* versus P or κ^{-1}

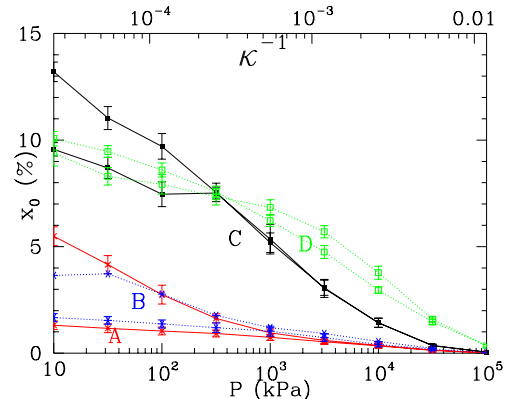

(c) x_0 versus P or κ^{-1}

FIG. 1: (Color online) Evolution of (a) solid fraction Φ , (b) backbone coordination number $z^* = z/(1-x_0)$ and (c) rattler fraction x_0 in pressure cycle for states A (red), B (blue), C (black), and D (green).

which we denoted as the A0 series. B states are similar to A ones, except that they are assembled with a small

coefficient of friction, $\mu_0 = 0.02$, as a crude model for imperfect lubrication in the fabrication stage. B states have a smaller density, and a slightly smaller coordination number. D states are the looser of the four series, with $\Phi \simeq 0.593$ under 1 kPa, less contacts and more than 10% of rattlers. Remarkably, vibrated C states are nearly as dense as the RCP one, but their contact networks are as tenuous as D ones, with even more rattlers. C configurations are thus denser than B ones, but much less coordinated. All those quantities and their evolution in a pressure cycle up to 100 MPa, and then back to the initial value, are graphically shown on Fig. 1. While density increases with P , so do the coordination numbers, most notably above a few MPa, but upon decompressing many contacts are lost and coordination numbers, if initially high, as in the A and B cases, end up with much lower values, similar to those of poorly coordinated C and D states. Solid fraction Φ displays very little hysteresis in such pressure cycles. A0 (frictionless) states behave very similarly to A ones. The data of Fig. 1 are merely recalled here in order to correlate them with the elastic moduli of the different sample series. Such state parameters and their evolution are commented in papers I and II, to which the reader can refer for more details (*e.g.*, information on force distribution and friction mobilization). A useful notation introduced in paper I, in which such quantities were used to characterize the width of force distributions is the following one, for reduced moments of normal forces N :

$$Z(\alpha) = \frac{\langle N^\alpha \rangle}{\langle N \rangle^\alpha}. \quad (17)$$

Another quantity, closely related to $Z(5/3)$ is useful to evaluate elastic energies from contact forces. If α_T denotes the ratio of tangential to normal stiffnesses (a constant parameter in our contact model) and if r_{TN} is the ratio $\frac{\|\mathbf{T}\|}{N}$ in any contact, then we define

$$\tilde{Z}(5/3) = \frac{\langle N^{5/3} (1 + \frac{5r_{TN}^2}{6\alpha_T}) \rangle}{\langle N \rangle^{5/3}}. \quad (18)$$

Such quantities will be used to estimate elastic moduli.

In paper I, we also discussed whether the degree of force indeterminacy of equilibrated packings could approach zero in frictional packings in the rigid, $\kappa \rightarrow +\infty$ limit – this being a known property of frictionless systems (as reviewed *e.g.*, in [32]). While the degree of force indeterminacy H is directly related to the backbone coordination number z^* in frictionless packings, for which

$$H = 3n(1 - x_0)(z^* - 6), \quad (19)$$

its value is more exactly evaluated, for non-vanishing intergranular friction coefficients, on defining a slightly corrected value of z^* , denoted as z^{**} :

$$z^{**} = z^* + \frac{2x_2}{3(1 - x_0)}, \quad (20)$$

where x_2 is the proportion of 2-coordinated grains. Such divalent particles are free to rotate about a line joining their 2 contact points, and roll on the surfaces of their two neighbor grains in contact, but those mechanisms do not lead to instabilities [1]. Then the degree of force indeterminacy is given by

$$H = \frac{3}{2}n(1 - x_0)(z^{**} - 4). \quad (21)$$

x_2 values raise to about 2.5% in configurations C and D, in which the ratio of the degree of force indeterminacy to the number of backbone degrees of freedom, *i.e.*, $H/[6n(1 - x_0)]$, does not reach values below 14%. Only in packings assembled with an infinite friction coefficient, like in [38] (called Z configurations in paper I) did we obtain nearly vanishing H values ($H/[6n(1 - x_0)]$ decreasing to about 3/100).

IV. ELASTIC MODULI

A. Numerical results

Elastic moduli of equilibrated configurations are evaluated as indicated in Section II C. The response to different global load increments provides different estimations of bulk modulus B and shear modulus G , which are averaged over, gathering results from 5 statistically equivalent samples (as we do throughout the present paper), the error bars on all graphs below corresponding to one standard deviation on each side of the mean (such error bars are often smaller than the symbols on the figures). Fig. 2 displays on logarithmic plots the pressure dependence of shear and bulk moduli in all five series A, A0, B, C and D during the first compression. Fig. 2 very clearly shows that the moduli are primarily sensitive to coordination number, with well coordinated samples A, B (and A0) displaying larger moduli than C and D, in which the contact network is more tenuous (see Fig. 1(b)). Moduli are much less sensitive to packing fraction Φ (Fig. 1(a)): C and D results are close to each other at low pressure. They are not strongly influenced either by the width of the force distribution: A and A0 states have almost the same moduli (only some values of G below 100 kPa differ by more than 5%), whereas the p.d.f. of normal forces strongly differ as pressure grows (as shown in paper II).

The increase of elastic constants with pressure naturally stems from the dependence of contact stiffnesses on the force they transmit, as expressed by Eqns. (3) and (4), and due to relation (2) the typical contact stiffness grows as $P^{1/3}$, which is the expected pressure dependence for macroscopic moduli. Power laws are often used to relate elastic moduli to confining stresses [16, 21, 22, 39], and possible origins for the observation of exponents other than 1/3 have been discussed by several authors [39, 40]. One possible explanation is the creation of new contacts under the effect of the increase of the confining pressure, which leads to a denser,

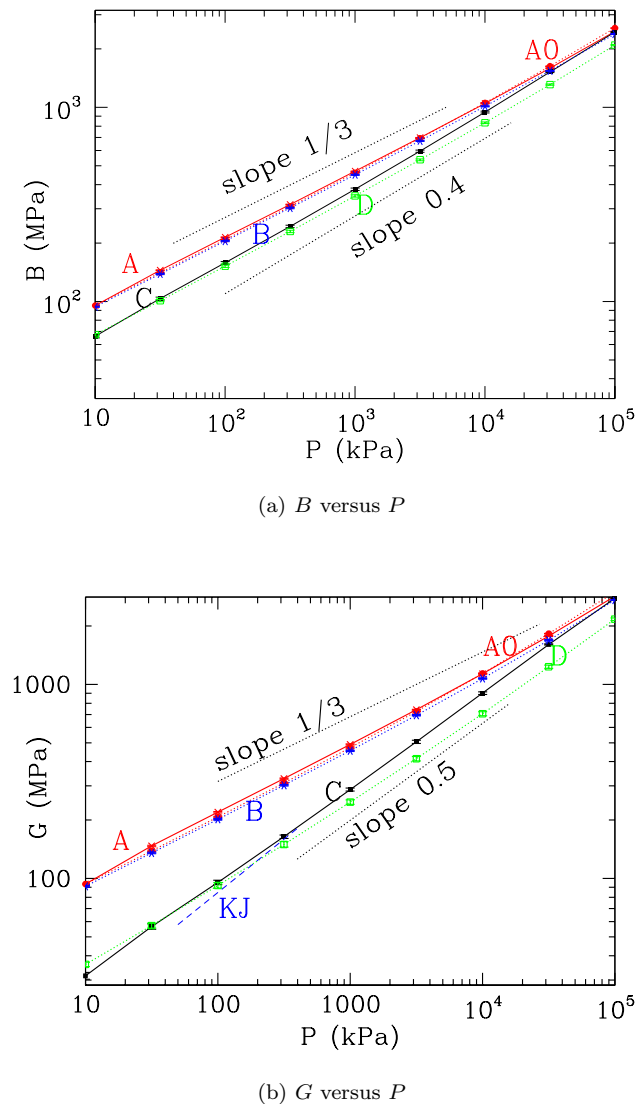


FIG. 2: (Color online) Bulk modulus B (a) and shear modulus G (b) versus confining pressure P for series A (red, crosses, continuous line), A0 (red, round dots, dotted line), B (blue, asterisks, dotted line), C (black, square dots, continuous line) and D (green, open squares, dotted line). Note that results for A, A0 and B are hardly distinguishable. The dashed blue line marked “KJ” corresponds to some experimental data between 50 and 400 kPa commented in Section VI

stiffer contact network. This mechanism appears in particular to account for the pressure dependence of elastic moduli in regular, crystal-like arrays of identical particles as in the experiments described in Refs. [5] and [7]. Due to the unavoidable slight lattice distortions one obtains on assembling imperfect and slightly polydisperse spheres, the contact coordination number, limited, in the rigid limit $\kappa \rightarrow \infty$, to 4 in 2D and 6 in 3D [32] is smaller than the nearest neighbor coordination number on the dense lattices studied (such as 12 for FCC in 3D [5] and

6 for the 2D triangular lattice [7]). This leaves a large number of neighbor pairs at a distance related to the width of the particle size distribution, where additional contacts are induced by higher pressures. This has been shown by numerical simulations [41] to produce a pressure dependence of moduli closer to $P^{1/2}$ in some pressure range, a phenomenon predicted in part by a theory presented in [42]. With general, amorphous packings, the situation is different because distances between neighbors that are not in contact are no longer related to a small polydispersity parameter, but are distributed, approximately as a power law in some range (see paper I [1]), in a way that is characteristic of the disordered geometry. Departures from the $P^{1/3}$ scaling are stronger in low z states (Fig. 2), and also larger in C configurations, which gain contacts the fastest at growing P , than in D ones. However, apparent power laws with exponents larger than $1/3$ are observed at very low pressures, when, from Fig. 1(b), the increase of z with P is rather slow. Moreover, in the case of C and D systems, the exponent of the power law fit for the pressure dependence of shear modulus G is significantly larger (about 0.5) than the one for bulk modulus B (about 0.4). These features are discussed in paragraph IV B below. Changes of ratio G/B as P grows are equivalent to changes of the Poisson ratio of the granular material, given by

$$\nu^* = \frac{3B - 2G}{6B + 2G}. \quad (22)$$

ν^* decreases only slightly as P grows for well coordinated states A and B, from $\nu^* \simeq 0.13$ at $P=10$ kPa to $\nu^* \simeq 0.09$ under 100 MPa. Its larger variations in poorly coordinated configurations C and D, for which it decreases from 0.3 to about 0.1 in the same range, corresponds to G increasing with P faster than B .

B. Simple prediction schemes and relations to microstructure

The simplest approximation scheme to estimate the values of elastic moduli, knowing the density and the coordination number, is based on the assumption of homogeneous strains (or, equivalently, of affine displacements). It was introduced, *e.g.* in [28], and it is also used by Makse *et al.* in [12] and [8] (where it is called an effective medium theory). It amounts to evaluating the stress increments corresponding to strain $\underline{\epsilon}$ using formula (12), in which the contact force variations are evaluated, *via* Eqn. (5), with relative displacements given by

$$\mathbf{u}_i - \mathbf{u}_j = \underline{\epsilon} \cdot (\mathbf{r}_j - \mathbf{r}_i).$$

Using the isotropy of the distribution of contact orientations, and replacing all normal forces by their average value in the computation of contact stiffnesses, this results, using relation (2), in the following estimates, in which α_T denotes the stiffness ratio K_T/K_N , a constant

in our contact model.

$$\begin{aligned} B^e &= \frac{1}{2} \left(\frac{z\Phi\tilde{E}}{3\pi} \right)^{2/3} P^{1/3} \\ G^e &= \frac{6 + 9\alpha_T}{10} B^e. \end{aligned} \quad (23)$$

One thus recovers the expected $P^{1/3}$ dependence, and obtains moduli proportional to $(z\Phi)^{2/3}$. Formulae (23) also predict a constant G/B ratio, and thus a constant Poisson ratio:

$$\nu^e = \frac{6(1 - \alpha_T)}{26 + 9\alpha_T} \simeq 0.032 \quad (24)$$

This latter estimation is considerably smaller than the measured values which are given above (shortly after Eqn. 22), as noted in [8]. This essentially stems from the inaccuracy of the estimated value of G [12], as we shall see. Eqn. 23 suggests to represent ratios


$$\begin{aligned} b_r &= \frac{B}{\tilde{E}^{2/3} P^{1/3}} \\ g_r &= \frac{G}{\tilde{E}^{2/3} P^{1/3}} \end{aligned} \quad (25)$$

as functions of $(z\Phi)^{2/3}$, which is done on Fig. 3. Fig. 3 shows that G^e is a significantly poorer estimate of G than B^e of B , as noted before [12], for samples of type A or B, and even more so in low coordination number configurations C and D. It also shows that the elastic moduli, as a first approximation, can be thought of as determined by z and Φ , the former quantity, as it varies more between different sphere packings, being the most influential. The present study can thus be regarded as a first step towards the formulation of a method to infer coordination numbers, which, as we stressed in paper I, are virtually inaccessible to direct measurements, from elastic properties. (It should nevertheless be recalled that the present work is limited to *isotropic* configurations, implying isotropy of fabric as well as isotropy of stresses). Interestingly, the configurations of lower coordination number obtained upon *decompressing* A and B ones after they first reach a high pressure level yield data points on Fig. 3 that stay close to the C and D ones corresponding to the same product $z\Phi$.


An interesting alternative to the direct use of formula (12) is to exploit the variational property expressed by (15), as explained in Appendix D. This shows that B^e and G^e are upper bounds to the true moduli. Accounting for the distribution of forces and Eqn. (3), those bounds can be slightly improved, yielding the analogs of the Voigt upper bound for the macroscopic elastic moduli of a mesoscopically disordered continuous material:

$$\begin{aligned} B &\leq B^{\text{Voigt}} = B^e Z(1/3) \\ G &\leq G^{\text{Voigt}} = G^e Z(1/3), \end{aligned} \quad (26)$$

where $Z(1/3)$ was defined in (17). $Z(1/3)$ is, by construction, strictly smaller than 1. For the bulk modulus, one

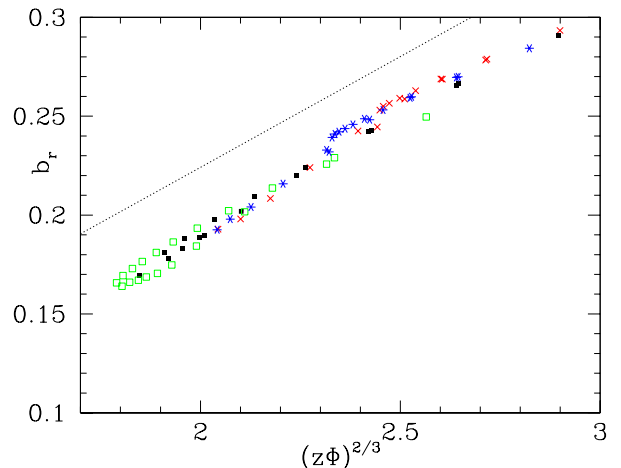

(a) b_r versus $(z\Phi)^{2/3}$

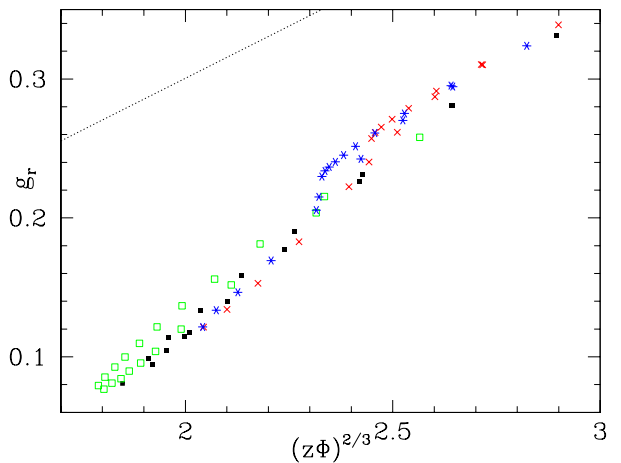

(b) g_r versus $(z\Phi)^{2/3}$

FIG. 3: (Color online) Reduced moduli, as defined in (25), in units of $\tilde{E}^{2/3} P^{1/3}$ as functions of $(z\Phi)^{2/3}$, same symbols and colors as on Fig. 1(a). The estimates given in (23) are plotted as straight dotted lines. Moduli are plotted for all configurations in the pressure cycle, showing an approximate collapse on a single curve.

can also take advantage of the second variational property, expressed by (16). As explained in Appendix D, this requires the use of a trial set of contact force increments which balance the applied load increment. When the stress increment is proportional to the preexisting stress, one may take increments of contact forces that are also proportional to their values. No such forces balancing a shear stress are available for isotropically prestressed configurations. On thus obtains (see Appendix D for details) a *lower* bound for B which is analogous to the Reuss bound for the macroscopic elastic bulk modulus

of a mesoscopically disordered continuous material. This lower bound B^{Reuss} involves the dimensionless quantity $\tilde{Z}(5/3)$ defined in (18), and enables one to bracket the bulk modulus:

$$\frac{B^e}{\tilde{Z}(5/3)} = B^{\text{Reuss}} \leq B \leq B^{\text{Voigt}} = B^e Z(1/3). \quad (27)$$

The ratio of the upper bound to the lower one is therefore related to the shape of the distributions of normal forces and to the mobilization of friction. Fig. 4 displays ratios B/B^e , B^{Voigt}/B^e , and B^{Reuss}/B^e versus (growing) pressure P in configurations A and C. These data show

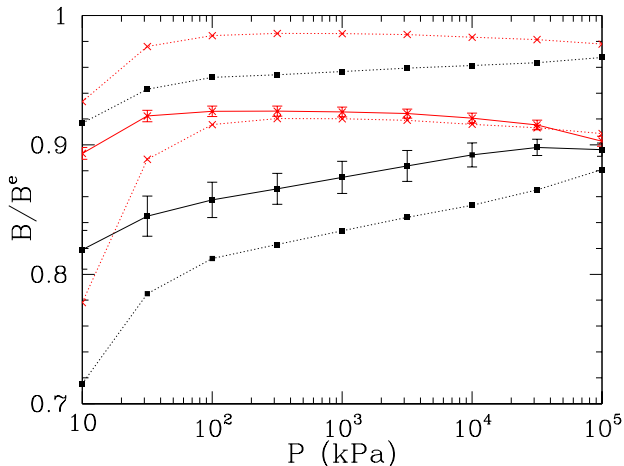


FIG. 4: (Color online) Ratio B/B^e (symbols connected with continuous line, error bars), and its Voigt and Reuss bounds (symbols connected by dotted lines) in configurations A (red, crosses) and C (black, square dots), during compression. B and D samples respectively behave similarly to A and C.

that in both cases of high (A) and low (C) initial coordination number, the bracketing of B given by (27) is quite accurate, the relative difference between upper and lower bounds being below 10% except at the lowest pressure for A, and around 15% for C. The Reuss estimate is better than the Voigt one in general. It is even excellent in the A case for all but the two lowest pressure values studied (as to the highest pressure, for which B appears to be slightly smaller than its lower bound, we attribute this to our neglecting the reduction of intercenter distances between contacting grains in the evaluation of the bounds). This agrees with previous results: since this estimate becomes exact when the trial force increments used are the right ones, it assumes that the shape of the normal force distribution and the level of friction mobilization do not change with pressure, which was indeed approximately observed in A samples for all but the lowest pressure (see paper II).

Yet, for G no Reuss estimate is available, and the use of the Voigt one with the factor $Z(1/3)$ hardly reduces the discrepancy between G^e and G . This factor can be read on Fig. 4, where it coincides with the upper bound; hence G^{Voigt} is only smaller than G^e by a few percent. It

thus overestimates the true shear modulus by 30 to 40% in well-coordinated states, and even by a factor of 3 in poorly coordinated ones at low pressure.

C. Fluctuations and more sophisticated prediction schemes.

The Voigt or mean field approach ignores fluctuations in grain displacements and rotations. An indicator of the amplitude of such fluctuations is the average of squared particle displacements:

$$\Delta^2 = \frac{1}{n^* \|\underline{\epsilon}\|^2} \sum_{i=1}^{n^*} \|\tilde{\mathbf{u}}_i\|^2, \quad (28)$$

with $\|\underline{\epsilon}\|^2 = \epsilon_1^2 + \epsilon_2^2 + \epsilon_3^2$, the sum running over the $n^* = n(1 - x_0)$ force-carrying grains. Fig. 5 displays the values of Δ^2 evaluated in all samples at the different values of the confining pressure. Δ^2 is distributed over some fairly wide interval in similar configurations, but is systematically larger for purely deviatoric stress increments than for isotropic pressure steps and has a clearcut decreasing trend as a function of backbone coordination number z^* . (To add data points with lower z^* on Fig. 5

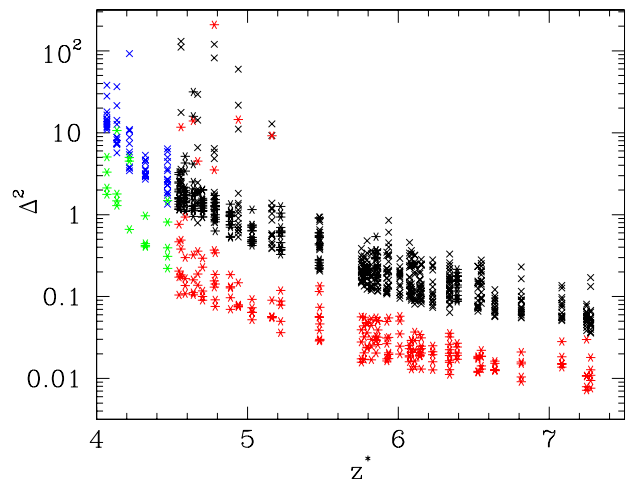


FIG. 5: (Color online) Δ^2 , as defined in (28), versus backbone coordination number z^* , for isotropic stress increments (red asterisks, green for Z states) and pure deviatoric ones (black crosses, blue for Z states).

we also used the Z series, infinite friction samples, as described in paper I and Section III, isotropically compressed and equilibrated at five pressure levels, from 1 to 100 kPa). This is consistent with the approximation that ignores fluctuations being less accurate for shear stresses than for isotropic ones.

More elaborate prediction methods for elastic moduli were proposed. Kruyt and Rothenburg [36, 43] considered two-dimensional assemblies of non-rotating particles, and succeeded in applying a variational approach

such as the one we use for bulk modulus B to the evaluation of shear moduli as well. Velický and Caroli [42] studied the case of an imperfect lattice system with contact disorder, as in the experiments of [5] and the simulations of [41]. Jenkins *et al.* [29] dealt with frictionless sphere packings. More recently, La Ragione and Jenkins [44] published an approximation scheme which is directly comparable to our simulation results, the results of which are denoted as LRJ below. For completeness, the corresponding formulae are written down in Appendix E.

Those estimation procedures improve upon the Voigt assumption that relative displacements are ruled by the average strain on considering small sets of displacements and rotations, either associated to one grain, or to a contacting pair. Those degrees of freedom are allowed to fluctuate while their surroundings abide by the Voigt assumption. Optimal values of the fluctuating variables are then to be determined on solving the corresponding system of equilibrium equations for the selected small set of degrees of freedom. Such approaches necessarily involve complex treatments of the random geometry of local grain arrangements, especially on attempting to express the predicted moduli with a limited amount of statistical data. In [45] we numerically check some of the approximations involved, on exactly solving the required set of local equilibrium problems. We show in [45] that the discrepancy between observed and predicted shear moduli is reduced, down to 50% in the worst cases of C and D samples under low pressures.

Here we now confront the LRJ predictions (see Appendix E for the complete analytical form) to our numerical data. We observe that the LRJ formulae do not improve the predictions of bulk moduli over the Voigt and Reuss bounds (27). Yet, as shown on Fig. 6, the estimates G^{LRJ} obtained for shear moduli are much better than the Voigt ones (26). Shear moduli in well-coordinated states A and B are accurately predicted, while the discrepancy in poorly coordinated systems C and D, from a factor of three with the Voigt formula, are down to about 50%-70% with the LRJ one under the lowest pressure levels.

LRJ formulae yield moduli that are proportional to average contact stiffnesses (in which we added a factor of $Z(1/3)$), with coefficients involving rational functions of the backbone coordination number z^* , and also the variance of the fluctuations in the number of contacts of backbone grains. The LRJ predictions still overestimates modulus G in poorly coordinated systems, in which we now test another kind of theoretical prediction.

V. THE CASE OF POORLY COORDINATED NETWORKS

The specific elastic properties of configuration series C and D, with their small coordination numbers, are reminiscent of frictionless packings [8, 46], in which a similar anomalous behavior of G as a function of pressure has been reported. Here we review these properties of

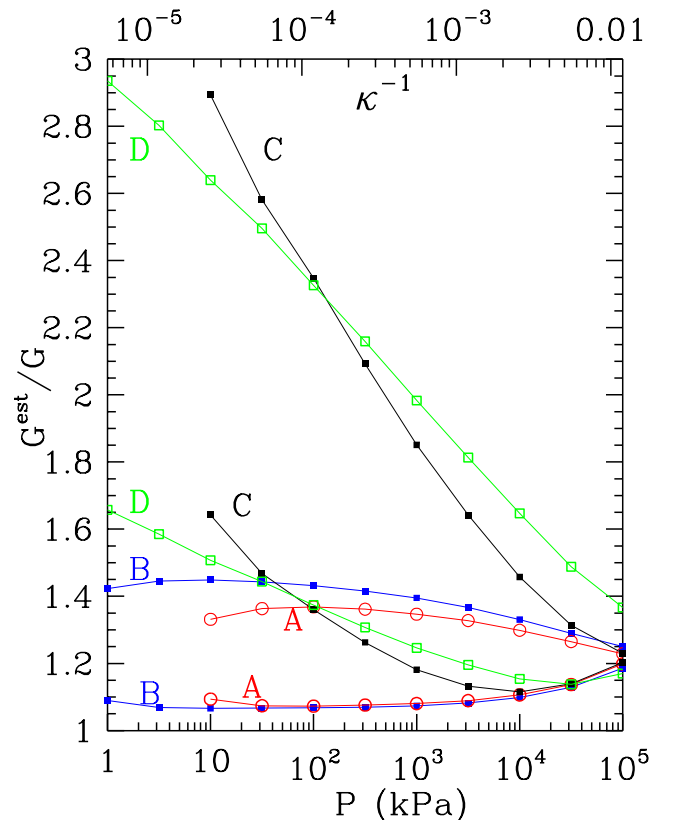


FIG. 6: (Color online) Ratio of estimated to measured values of shear moduli, G^{est}/G , with $G^{\text{est}} = G^{\text{Voigt}}$ (larger values) and $G^{\text{est}} = G^{\text{LRJ}}$ (smaller values), versus P or κ^{-1} , in sample series A (red), B (blue), C (black) and D (green).

packings with no tangential forces (Section V A), and we discuss a possible explanation [47], and its applicability to poorly coordinated frictional packings (Section V B).

A. Frictionless packings

Although samples of series A0 were confined with no mobilization of friction, elastic moduli shown on Fig. 2 have been computed with tangential elasticity in the contacts, just like, *e.g.* in Ref. [12]. It is assumed for state A0 that friction is not mobilized in the preparation process, or in other words samples are perfectly annealed to a state of lowest mechanical energy, but the response to some stress increment implies tangential forces in the contacts. Results are of course different if contacts are still regarded as frictionless on evaluating elastic properties. Fig. 7 compares this new set of values, which we denote as A00, to A0 ones. Bulk moduli (Fig. 7(a)) are only slightly higher (about 10% at low pressure) with tangential elasticity. A00 values, corresponding to frictionless packings, are the ones already studied in paper I [1, Section III], where, thanks to the isostaticity prop-

erty they were well described by a simple prediction. The Reuss type estimate of B , Eqn. (27) and (23), actually coincides with this prediction made in paper I, except that the values of z and Φ are the ones corresponding to the current value of the pressure. Both approaches are based on the assumption that the distribution of force values in sample series A0, once normalized by the applied pressure level, does not change during isotropic compression. Hence their success, since this condition is almost exactly satisfied (as shown in paper II [2]).

The small influence of tangential elasticity on bulk moduli, which is responsible for the difference in B values between A0 and A00 series, is not surprising, as both the Voigt and the Reuss-like approaches, which restrict the values of B to the interval given by (27), lead to the assumption of vanishing tangential forces.


The shear modulus, on the other hand, as noted in refs. [8, 46], is singular in frictionless packings under isotropic stresses: while values of G in the A0 series vary approximately proportionally to B , and are of the same order, as observed above in Sec. IV A, shear moduli of frictionless systems A00 (Fig. 7(b)) are considerably lower, and vary faster with P . This increase is very well fitted by a power law with exponent 2/3, in agreement with [46]. An explanation for the singular behavior of G is suggested in [47] (see also [48]), as follows. First, some of the pressure dependence of G is simply due to the influence of pressure on average contact stiffness, which is proportional to $P^{1/3} \tilde{E}^{2/3} Z(1/3)(\Phi z)^{-1/3}$, and one should therefore rather explain the pressure dependence of the ratio of G to this average stiffness. Then it is argued that this amplitude is proportional to the degree of force indeterminacy, or to $z^* - 6$. More precisely, the shear modulus should scale as the degree of force indeterminacy per unit volume, or equivalently as $(z^* - 6)(1 - x_0)\Phi$. This is the crucial part of the argument. Leaving aside a discussion of its justification (which would require detailed calculations of sets of self-balanced contact forces and response functions within the contact networks) we check here for its practical validity. To do so, we define a reduced shear modulus g_a as

$$g_a = \frac{Gz^{1/3}}{\tilde{E}^{2/3} P^{1/3} Z(1/3)(1 - x_0)\Phi^{2/3}}, \quad (29)$$


and we study its variations with z^* . Finally (see also [38]), Ref. [47] suggests to evaluate the increase of coordination number with pressure on relating both quantities to the increase in packing fraction above rigidity threshold $\Delta\Phi$. Such a relation between P and $\Delta\Phi$ in isostatic frictionless packings was written in [1], with $P \propto (\Delta\Phi)^{3/2}$. The additional ingredient is a scaling form of the increment of z^* with $\Delta\Phi$:

$$z^* - 6 \propto \Delta\Phi^{1/2}. \quad (30)$$

To justify (30), a homogeneous shrinking approximation is adopted, as in paper II [2], based on the assumption that the gap-dependent near neighbor coordination number $z(h)$ grows like $z(h) - 6 \propto h^{0.5}$. However, as shown

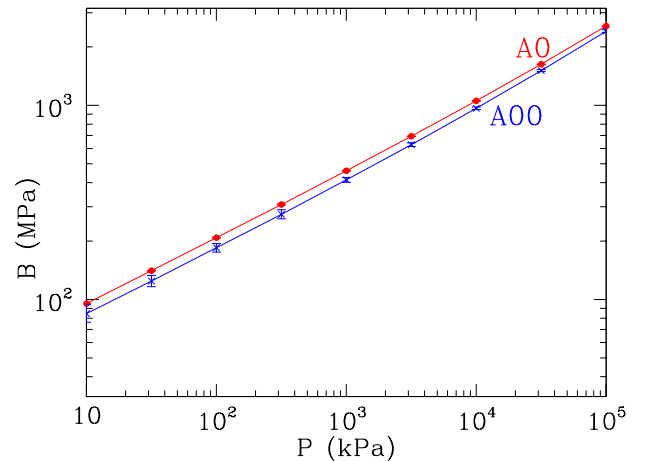

(a) Bulk modulus.

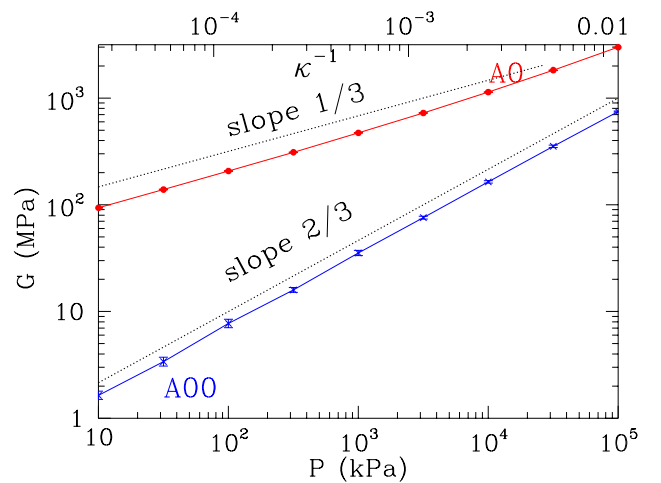

(b) Shear modulus.

FIG. 7: (Color online) Elastic moduli of samples A0 prepared at different pressures without friction, computed with (A0) and without (A00) tangential elasticity, A00 results corresponding to completely frictionless packings.

in [1] we observed an exponent 0.6 instead, and our data therefore do not confirm this part of the argument.

Nevertheless, the proportionality of the singular amplitude g_a of the shear modulus to $z^* - 6$ is accurately satisfied, as shown on Fig. 8. The linear fit of the dependence of g_a on z^* , through the 6 first data points, is very good and predicts a vanishing modulus for $z^* = 5.994 \pm 0.008$.

B. Packings with intergranular friction

In paper I we concluded that frictional packings prepared in low coordination states did not approach iso-

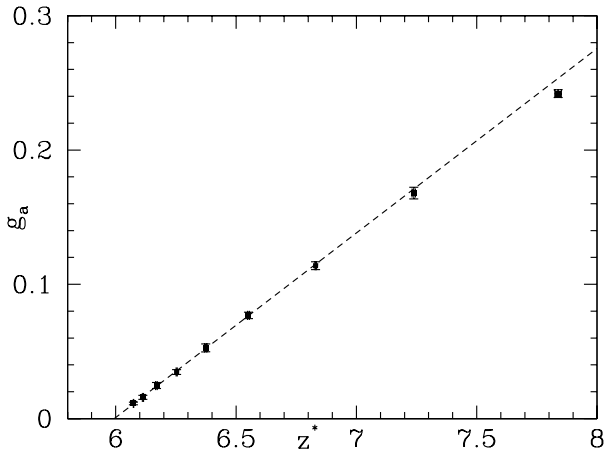


FIG. 8: Reduced shear modulus g_a , defined by (29), in frictionless configurations A00 versus backbone coordination number z^* . The straight line is the best linear fit through the 6 leftmost data points.

staticity under low pressure. However, one may test whether the amplitude g_a varies linearly with the degree of force indeterminacy when it is small enough, even if it does not approach zero. The Z states, on the other hand (see Section III and paper I [1]), were prepared with an infinite friction coefficient and have nearly vanishing force indeterminacy at low pressure. Fig. 9, in which g_a data for states C, D and Z are plotted versus the corrected backbone coordination number z^{**} , which determines the degree of hyperstaticity per degree of freedom by (21), shows that the linearity is very well satisfied for Z states.

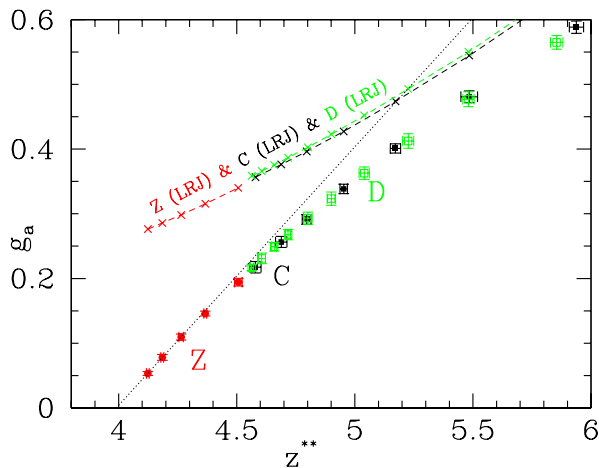


FIG. 9: (Color online) Amplitude g_a (Eqn. 29) versus z^{**} , as defined in (21), in samples of types C (black), D (green) and Z (5 lower data points, red). The dotted line is a linear fit to the 4 lowest Z data points. The LRJ predictions are shown for all three configuration series C, D, Z, as indicated (crosses joined by dashed lines, same color code).

Z, C and D points lie approximately on the same curve,

showing that the macroscopic modulus is controlled by z^{**} , in spite of the differences in the structures of states C, D and Z. (Due to the greater micromechanical changes observed upon *reducing* the pressure, the data points pertaining to C and D states on the decreasing branch of the pressure cycle of Fig. 1 lie on a different curve, not shown on the figure.) The linear fit still approximately applies to the lowest values for D and C. As expected, the linear fit predicts $G = 0$ for $z^{**} = 3.99 \pm 0.02$, *i.e.*, a shear modulus vanishing proportionally to the degree of force indeterminacy. Z configurations have a larger population of rattlers and divalent grains: $x_0 \simeq 0.184$ and $x_2 \simeq 0.068$ at 1 kPa. Consequently, on fitting g_a versus z^* instead of z^{**} , g_a would appear to vanish unambiguously below $z^* = 4$, for the value $z^* = 3.93 \pm 0.02$.

Fig. 9 also displays the values of amplitudes g_a predicted by the LRJ formulae [44], as discussed in Section IV C. As should normally be expected for such an estimation procedure, based on the local equilibrium of one pair of grains embedded in an elastic medium, the LRJ approach is unable to capture the vanishing of shear moduli in the $z^{**} \rightarrow 4$ ($H \rightarrow 0$) limit, since the rigidity properties of tenuous networks are determined by more collective effects. The low level of force indeterminacy provides a complementary approach to the estimation schemes evoked in Section IV C to predict the values of shear moduli in isotropically compressed packings.

We conclude therefore that the proximity of a state devoid of force indeterminacy, however unreachable, explains the anomalously fast increase of the shear modulus with the pressure for low coordination frictional packings, as observed on Figs. 2 and 3. As to the increase of the degree of hyperstaticity, or of z^{**} , with pressure, its prediction seems to be even more difficult than in the frictionless case. What would be needed is an accurate prediction of small changes in z^* , which, as observed in [2] (paper II) the simple homogeneous shrinking assumption does not provide, due, in particular, but not only, to its inability to deal with the recruitment of rattlers by the growing backbone.

The proximity of a “critical” value of the number of contacts on the backbone also entails specific properties of the eigenvalues of the stiffness matrix (the “density of states” in the language of solid-state physics), with a large excess of soft modes [46, 49]. A similar behavior, both for the eigenmodes of the stiffness matrix and for some shear elastic constant was observed in [30] in 2D simulations of anisotropic states. From this one set of results in anisotropic packings and from the Reuss approach to estimate the bulk modulus one may deduce that the non-singularity of B , as opposed to G , directly stems from the *isotropic* state of stress on which load increments are applied. On increasing P , in a good approximation (the better the lower the degree of force indeterminacy), one just rescales the contact force values. Load increments that are not proportional to the pre-existing load, on the other hand, tend to produce large fluctuations (see Fig. 5) and soft responses in poorly co-

ordinated contact networks.

VI. COMPARISON WITH EXPERIMENTAL RESULTS

The assembling procedure of states B and C (Sec. III) can be regarded as idealized models for lubrication and vibration. Jia and Mills [22, 24] measured sound wave velocities in glass bead packings, some samples being densified by repeated taps on the container, and others mixed with a very small quantity of a lubricant (trioleine). The beads were placed in a cylindrical container and then compressed by a piston, transmitting a confining pressure. Velocities of longitudinal and transverse sound waves propagating in the vertical direction (orthogonal to the piston) were measured in the 70 kPa–800 kPa range. Those velocities, which we denote as usual as V_P and V_S , relate for an isotropic material to bulk and shear moduli and mass density ρ as

$$V_P = \sqrt{\frac{B + \frac{4}{3}G}{\rho}} \quad \text{and} \quad V_S = \sqrt{\frac{G}{\rho}}.$$

Fig. 10 displays the sound velocities in both types of samples, along with the (often quoted) results of Domenico [9], measured on a glass bead sample in a higher pressure range. Within the range of vertical pressure P investigated in the experiments of [22], the packing fraction of dry beads varies between 0.633 and 0.637, while lubricated ones are less dense, Φ ranging between 0.613 and 0.617. Sound velocities are nevertheless larger in lubricated packings.

Comparisons with our numerical data, also shown on Fig. 10, in spite of the differences in preparation procedures (which are idealized, and involve somewhat arbitrary choices of parameters in simulations) and loading (oedometric compression in experiments, isotropic compression in simulations), reveal some interesting qualitative convergences and semi-quantitative agreements. Specifically, we note that:

- Numerical “lubricated” samples B are also less dense, but stiffer than numerical “vibrated” samples C.
- Sound velocities in B samples increase with P slower than in C ones, like velocities in laboratory samples prepared by vibration increase slower than in lubricated ones.
- Numerical C samples are better models for dry experimental packings assembled by vibration than A ones.

One may therefore attribute the difference in sound velocities reported in [22] between dry and lubricated packings to a difference in coordination number, like in numerical states B and C. (Such an interpretation differs

from the one set forth in [22], which relies on the filling of open interstices by the lubricant).

The traditional numerical route to obtain dense samples, *i.e.* the use of a vanishing or low friction coefficient as for systems A and B, fails to reproduce the elastic properties of dense samples assembled by vibration. Those appear to be better simulated with the newly introduced numerical procedure resulting in C samples, which have a much lower coordination number for the same density. Laboratory samples with a solid fraction approaching the RCP value might well, especially if their preparation involves vibrations or tapping, possess as small a density of force-carrying contacts as our numerical samples of type C ($z \simeq 4.05$).

Such a conclusion, in favor of low-coordinated numerical samples as better models for experimental dense packings of dry beads than conventional, A-type ones, appears to contradict the results of Makse *et al.* [8, 12]. Those authors simulated what we denoted as the A0 sample series, and reported good agreements with Domenico’s results [9] and with their own measurements. We checked that the agreement between their numerical results and our A0 data was excellent. We attribute the conflicting conclusions to their comparison being done in a much higher pressure range than the one of Jia and Mills’ experiments: as apparent on Fig. 10, the confining pressures in Domenico’s experiments are all above 2 MPa. Likewise, P values all exceed several MPa in the experiments performed by Makse *et al.* In this range, differences between A and C samples, as apparent on Fig. 10 for sound velocities, as well as on Fig. 1(b) for coordination numbers, tend to dwindle as P increases. The discrepancy between numerical results on A-type systems and experimental results on dry bead packings is much lower under high pressure. Yet, numerical samples of type C still fit the experimental data better. The apparent exponent in a power-law increase of sound velocities with P , *i.e.* the slope on Fig. 10, is, in particular, better reproduced by C data than by A ones. On discussing such a high pressure range, one should nevertheless keep in mind the possible occurrence of non-elastic behavior in the contacts, as pointed out in [2] (paper II), where the maximum stress levels in contact regions were estimated.

The fast increase of G as a function of P in C samples is not observed in the experimental results of Jia and Mills. Those also, on assuming for simplicity that the material is isotropic in their experiment, correspond to larger (0.32 to 0.34) Poisson ratios than in simulations, which furthermore do not seem to decrease as the pressure grows. However, these data are bound to be affected by stress anisotropy.

In this respect, a comparison of numerical results with the data of Kuwano and Jardine [6] is easier, as those were measured in glass bead samples under *isotropic* stress states, from about 50 to 400 kPa. The samples of Kuwano and Jardine have similar densities to D ones ($\Phi \simeq 0.59$), and are initially made by air pluviation. The values of shear moduli are close to the nu-

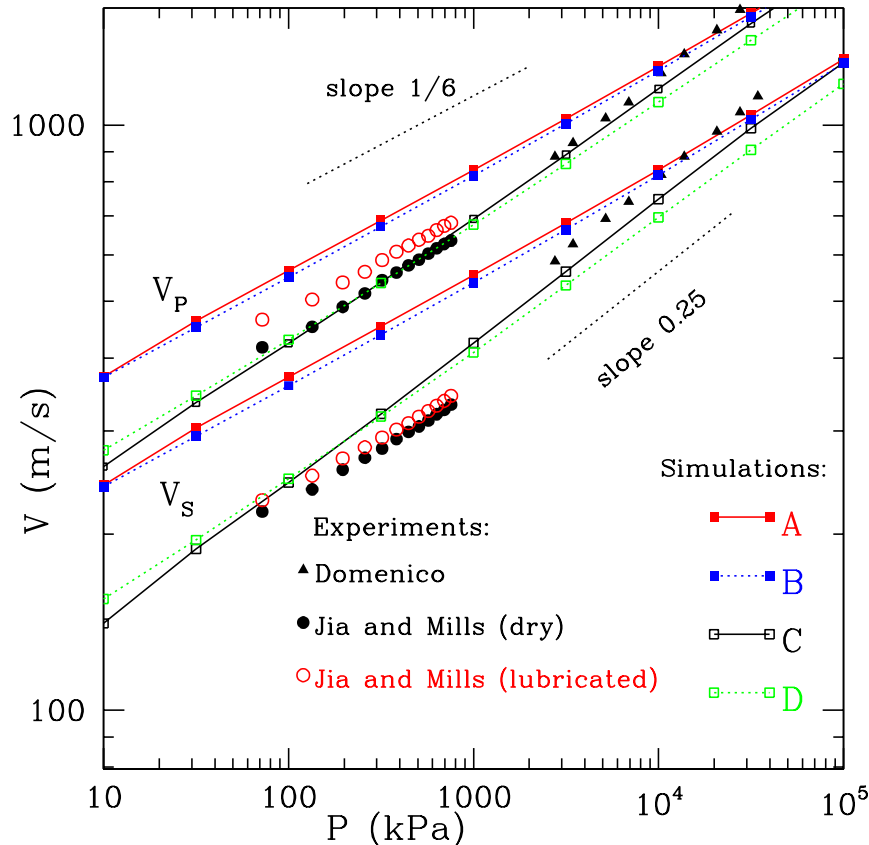


FIG. 10: (Color online) Sound velocities V_P and V_S versus confining pressure P on double logarithmic plot for the experimental dry (vibrated) and lubricated samples of Jia and Mills, and of Domenico, to which numerical values for simulated states A, B, C and D are compared.

merical values for C and D states, and vary with P even faster, as $G \propto P^{0.55}$. The power law fit through these data correspond to the line marked “KW” on Fig. 2(b). Kuwano and Jardine, combining static small-strain tests and sound velocity measurements, could evaluate the 5 independent elastic moduli of the transverse isotropic granular material assembled under gravity, by a pluviation procedure. To compare our numerical results, obtained in isotropically assembled systems, with theirs, we ignored the moderate effect of the fabric anisotropy on elastic moduli and used the moduli corresponding to a shear strain in the vertical plane in Fig. 2(b), the shear modulus in the horizontal plane being about 7% larger. Another similarity between our results in D or C states and the data of [6] is the pressure dependence of the two Poisson ratios ν_{vh} and ν_{hh} which couple stress and strain components in 2 different directions that define, respectively, vertical and horizontal planes. Despite some scatter in the measured values of these ratios, ν_{vh} and ν_{hh} show a marked decreasing trend between $P=80$ kPa and $P=400$ kPa. Finally, we compare the Young moduli measured in [6] in vertical and horizontal directions to our numerical values in states A to D on Fig. 11. Our

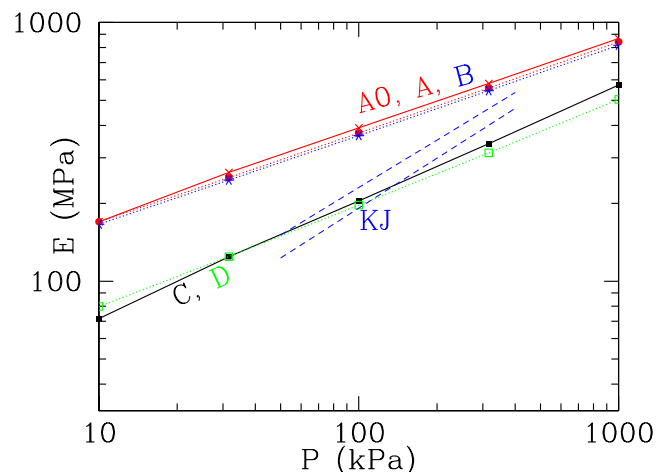


FIG. 11: (Color online) Young modulus in numerical samples A, A0, B, C, D, labelled with same colors and symbols as on Fig. 10, compared to fits through data points of Kuwano and Jardine (dotted lines, KJ) [6], with two sets of values because of fabric anisotropy.

numerical values for Young modulus E^* in systems with low coordination numbers are similar to those results, but the pressure variation seems faster (with exponent ~ 0.6) in experiments.

We conclude therefore that, although more systematic confrontations with experimental results are necessary, some features of the moduli in low coordination numerical packings are apparently observed in the rather loose glass bead samples of Kuwano and Jardine.

VII. ELASTIC RÉGIME

The elastic moduli which we are presently discussing express the relationship between small stress and strain increments. We now wish to evaluate the elastic range, and to explore the origins of the breakdown of elasticity for larger increments. Motivated by comparisons with experiments, we tested the predictions of linear elasticity, as evaluated with the moduli obtained from the stiffness matrix, versus the full MD simulation for small and slowly applied load increments, in the case of a *triaxial axisymmetric compression*. This test, familiar in geomechanical engineering [50, 51, 52], consists in increasing one stress component, say σ_1 , while the other 2 are kept constant at the initial value of the isotropic pressure in the initial state: $\sigma_2 = \sigma_3 = P$. More often, in the laboratory, one controls strain component ϵ_1 (called “axial strain”) with the motion of a piston, imposing a constant, slow strain rate $\dot{\epsilon}_1$, while the lateral stresses are maintained by the pressure of a fluid surrounding the sample, which is wrapped in an impervious membrane. It is customary to express the results of such a test with two curves, representing, as functions of axial strain, the *deviator stress* $q = \sigma_1 - \sigma_3$ and the *volumetric strain* $\epsilon_v = \epsilon_1 + \epsilon_2 + \epsilon_3$, the initial isotropic state being chosen as the origin of strains.


One should have in the quasistatic régime (small enough $\dot{\epsilon}_1$), within the linear elastic range, for small enough $\underline{\epsilon}$,

$$\begin{aligned} q &= E^* \epsilon_1 \\ \epsilon_v &= (1 - 2\nu^*) \epsilon_1, \end{aligned} \quad (31)$$


where $E^* = \frac{9BG}{3B+G}$ and ν^* (see Eqn. 22) are respectively the Young modulus and the Poisson ratio of the material in the initial state.

We simulated triaxial compressions for small axial strains and compared the resulting deviator stress and volumetric strain curves to (31). To minimize dynamical effects in simulations of quasistatic behavior, the inertia parameter I was kept below 10^{-4} or even 10^{-5} for the most fragile, low pressure samples. (I is defined by $I = \dot{\epsilon} \sqrt{\frac{m}{aP}}$ with m denoting the mass of one grain, see papers I and II [1, 2]). Fig. 12 shows the typical results of such a comparison in the case of one C sample series,

under isotropic initial pressures P growing from 10 kPa to 1 MPa. This comparison first shows that full MD com-

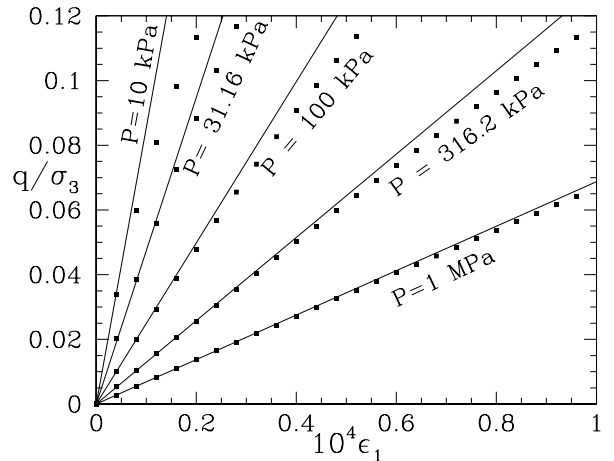

(a) Deviator stress normalized by $P = \sigma_3$ versus axial strain ϵ_1 , for the five P values indicated.

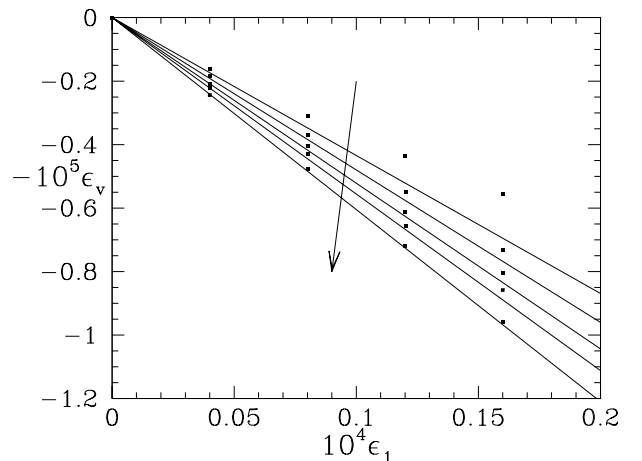

(b) Volumetric strain $-\epsilon_v$, showing contractance, versus axial strain, same P values, growing according to arrow.

FIG. 12: Deviator stress (a) and volumetric strain (b) versus axial strain in beginning of triaxial compression of a type C sample. Dots show MD results of triaxial compression while straight lines have slopes given by (31). The volumetric strain is shown with an axis oriented downwards to better visualize the *decrease* in sample volume, which contrasts with its dilatancy for larger strains.

putation results do admit, in excellent approximation, as slopes of the tangents to the curves at the origin, the appropriate values deduced from the evaluation of elastic moduli by the stiffness matrix approach, as expressed by (31). This confirms the statements made in Sec. II C, and checked in Appendix A about the definition of elastic moduli: this definition makes sense as a very good ap-

proximation in spite of the slight directional dependence of contact stiffness matrix $\underline{\mathcal{K}}$.

The deviator curves deviate significantly from the initial tangent straight line in this case for ϵ_1 growing from $\sim 10^{-5}$ to $\sim 10^{-4}$ as P grows through the investigated range, between 10 kPa and 1 MPa. This limit, if expressed with stress ratio q/σ_3 , shows less variations with $\sigma_3 = P$, with a slow increase, starting around $q/\sigma_3 \simeq 0.05$. The volumetric strain curve has an initial slope which increases with pressure, in agreement with the results on Poisson ratios (Sec. IV A). Deviations from the linear range of (31) appear a little sooner, for ϵ_1 slightly below 10^{-6} at 10 kPa, increasing to a few times 10^{-5} at 1 MPa.

In the literature on sand properties [6, 15, 16], it is often observed that the approximately linear elastic range about a prestressed reference state extends to strains of order 10^{-6} or 10^{-5} . On Fig. 13, we plotted the value of ϵ_1 for which the deviator stress starts to deviate from (31) by more than 5%, versus the confining pressure, for series A, C, and D. Recalling that most experimental re-

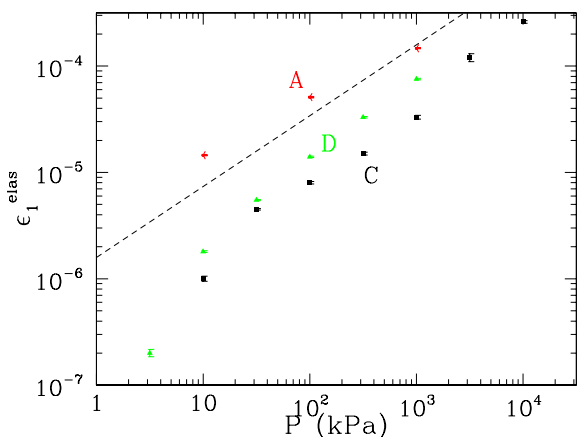


FIG. 13: (Color online) Threshold ϵ_1^{elas} above which q differs from $E\epsilon_1$ by more than 5%, versus P , for series A (red), C (black) and D (green). The dotted line has slope 2/3.

sults are collected in the range $50 \text{ kPa} \leq P \leq 1 \text{ MPa}$, these data confirm the experimental observations [15] on sands in terms of order of magnitudes for all three sample series. However, they also witness a systematic growth of the elastic threshold ϵ_1^{elas} with P , roughly as $P^{2/3}$. This suggests a constant elastic deviator interval relative to the confining pressure, q^{elas}/P , on assuming $E \propto P^{1/3}$. Figs. 14 and 15 show that the elastic range is better expressed in that form, as the threshold ratio q^{elas}/P displays much smaller variations as a function of P : unlike Fig. 13, those graphs show stress intervals on a linear scale. Expressing the extension of the linear elastic régime in terms of strains, as done in the literature on sands, allows one to gather the different sample series within the same range of magnitudes around 10^{-5} , provided the confining pressure stays within the interval that is most often investigated in experiments.

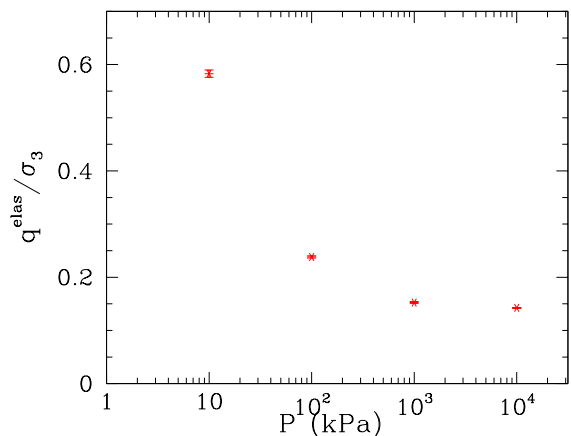


FIG. 14: Stress ratio q^{elas}/P above which q/E differs from ϵ_1 by more than 5%, versus P , for series A.

However, the systematic dependence on pressure is better accounted for on expressing the upper limit of the linear elastic range in terms of stress increments, relative to the confining stresses. The trend in low-coordinated systems C and D is an increase of the linear elastic in-

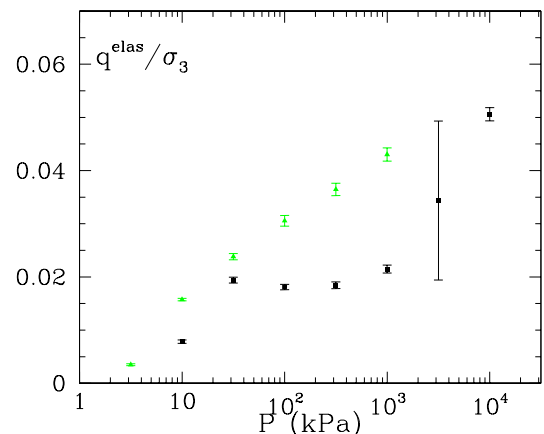


FIG. 15: (Color online) Stress ratio q^{elas}/P above which q/E differs from ϵ_1 by more than 5%, versus P , for series C (black, lower data points) and D (green).

terval, expressed as a stress ratio, with P . At the lowest pressure, the smallness of this interval (typically about 10^{-3} for ratio q/P in D samples under $P = 1 \text{ kPa}$) is characteristic of the larger fragility of tenuous networks, a phenomenon, once again, reminiscent of the situation of nearly isostatic force-carrying structures in frictionless packings under low pressure. In the limit of rigid grains, frictionless systems should behave as described in [53]: the deviator stress increments causing exactly isostatic 2D packings of rigid disks to fail and rearrange were found to approach zero as an inverse power of the number of particles n in the limit of large systems, $n \rightarrow \infty$. Series A configurations, on the other hand, have decreasing linear

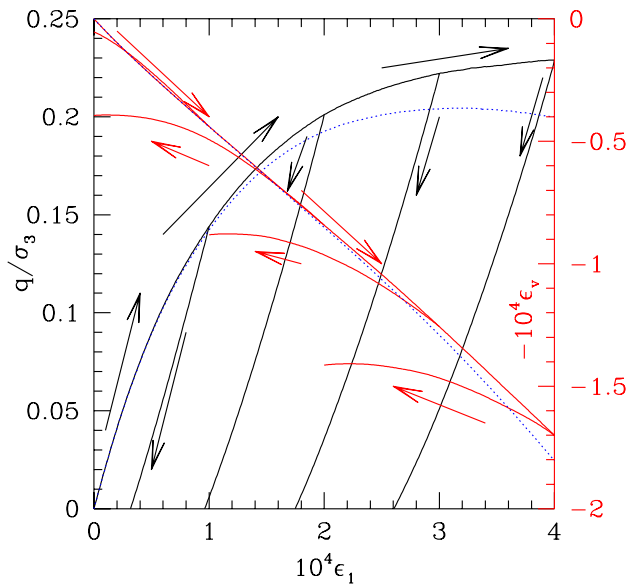


FIG. 16: (Color online) Deviator stress (black, left axis) and volumetric strain (red, right axis) versus axial strain in triaxial compression for small strains, with unloading curves, in a D sample initially under $P=100$ kPa. The blue dotted curves show the results of a calculation with the sole contacts that are initially present.

elastic intervals as a function of pressure. This is due to the increase of friction mobilization, which leads to larger non-elastic terms in the response to load increments.

So far we have been testing the accuracy of *linear* elasticity, *i.e.*, the predictions of (31) with the initial moduli. It is known from experiments that granular materials cease to be elastic outside this linear régime. This may be checked on testing for reversibility in a strain cycle. The effects of unloading from various points on the triaxial compression curve are shown on Fig. 16, in a type D sample with $\sigma_2 = \sigma_3 = 100$ kPa. On reversing the sign of $\dot{\epsilon}_1$, while still maintaining constant lateral stresses $\sigma_2 = \sigma_3$, one observes that the unloading curve starts with a slope close to the initial slope of the loading curve, those common slopes being in fact equal to the elastic moduli corresponding to the linear response for very small strain increments. Fig. 16 shows that the response to a deviator stress is no longer reversible as soon as it ceases to abide by linear elasticity. Departures from reversibility amount to a large proportion of strains for relative stress increments of order 10^{-1} . The response to an isotropic load increment is much closer to reversibility, even for much larger stress variations, as shown on Fig. 17, which displays the stress-strain curve in an isotropic pressure cycle. As P varies by a factor of 2, about 93% of the volume increase is recoverable. Only for the large pressure cycles as depicted on Fig. III (showing results of paper II [2]) can one observe notable irreversible changes, in coordination number rather than

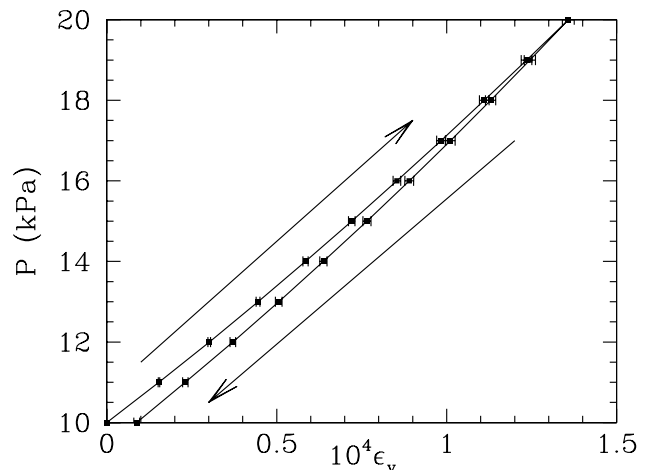


FIG. 17: Isotropic pressure increase versus relative volume change in pressure cycle, P growing from 10 to 20 kPa in C samples, and then decreasing back to 10 kPa.

in density. One thus finds again that the response to increments in load *intensity* (here: isotropic compression) strongly differs from the response to changes in load *direction* (here: deviator stress).

Returning to deviatoric stress increments, as the onset of irreversibility coincides with the breakdown of linearity mentioned above, the lack of reversibility shown on Fig. 16 has two different origins. One is the mobilization of friction, and the second is the failure of the contact network: the packing eventually breaks apart and rearranges. In order to detect the occurrence of this latter kind of event, we computed the response in the beginning of a triaxial compression of some samples with MD calculations in which only the initially present contacts, in the isotropic state, are taken into account. One thus tests the ability of the initial contact network to support different stress values. One then observes, as shown on Fig. 16, that the initial contact network proves unable to support a deviator stress beyond a certain limit: the q versus ϵ_1 curve reaches a maximum if $\dot{\epsilon}_1$ is controlled. This witnesses the propensity of the packing to become unstable and gain kinetic energy before it finds a new contact network that is able to support a larger deviator. This happens the sooner the larger the stiffness parameter κ in systems with low coordination numbers. Thus the corresponding ratio q/σ_3 decreases from about 0.2 in the example of Fig. 16, corresponding to a D sample under 100 kPa, to, typically, 0.1 under 3 kPa, and 0.05 under 1 kPa. In this respect (as for the values and pressure dependence of shear moduli) low coordination frictional packings exhibit, in a weakened form, similar singular behaviors to frictionless ones. The opposite behavior is that of A-type packings, with a very large coordination number. As shown on Fig. 18, the irreversibilities are smaller and the initial contact network proves able to withstand considerably larger relative deviator stresses, $q/\sigma_3 \sim 1.1$ under 100 kPa. In these respects, the be-

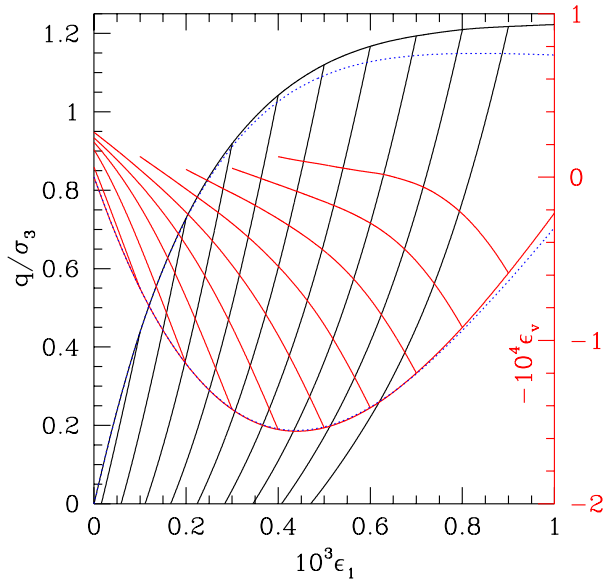


FIG. 18: (Color online) Analog of Fig. 16 in a sample of type A. Note the different scales.

behavior of A packings under shear is therefore somewhat intermediate between that of low coordination systems C or D under not too low confining stress, and the response to isotropic pressure increases. The behavior of A samples under triaxial compression is to a large extent determined by the response of the initial contact network, and the rise of deviator q as a function of axial strain is very fast. This is a typical feature of well-coordinated packings, as studied in [54]. In Refs. [54] and [55], two different types of strain are distinguished: those due to the deformability of contacts, and those stemming from network failures and rearrangements. As long as the first type of strains is the only one present, the behavior is close to that of the initial contact network. Beyond the stability range of the initial contact network, the effect of rearrangements dominates [55], strains are produced by local instabilities which can be described with a rigid grain model [56].

Refs. [55, 57] clearly show that well-coordinated isotropic packings (2D analogs of A systems) can support rather large deviator stress increments in the $\kappa \rightarrow \infty$ limit, whatever the sample size. Systems with lower coordination numbers appear to exhibit intermediate behaviors between this one and the “fragility”, defined as the propensity to rearrange for arbitrary small stress increments in the large system limit [32, 53, 55, 58], of assemblies of rigid, frictionless grains. The stability range of given equilibrium contact networks extends to smaller stress increment intervals in C or D-like packings, but we expect it to remain finite for arbitrary low pressure levels. These properties, and the distinction of two types of strains, are further explored and discussed in a forth-

coming paper [59].

VIII. CONCLUSIONS AND PERSPECTIVES

Our numerical results can be summarized as follows.

Elastic moduli of granular packings are primarily sensitive to the stress level, *via* the average contact stiffness, which is proportional to $P^{1/3}(z\Phi)^{-1/3}$ under pressure P . Once this effect is taken into account, important differences remain between the elastic properties of different packing structures, and systems assembled with the same density might exhibit large variations in their moduli, since those are essentially related to coordination numbers. Under isotropic pressures, one should distinguish between bulk and shear moduli. The bulk modulus, in all studied configurations, is efficiently evaluated by the Voigt and Reuss-like bounds, the ratio of which is limited by the force distribution and does not have wide variations with the microstructure of cohesionless packings. In general, we expect a difference between the responses to changes in load intensity on the one hand, and to changes in stress direction on the other hand. In isotropic systems, the latter correspond to purely deviatoric stresses, the effect of which differs the most from that of hydrostatic pressure increments in low coordination contact networks. In such cases shear moduli are anomalously small and increase faster with the confining pressure. In well coordinated states, such as A and B, one expects to be able to obtain satisfactory estimates of B and G moduli on using improvements of the Voigt approximation, based on locally independent fluctuations about average strains. Moreover, the additional stiffening effect of the increase in coordination number, due to compression, might, for pressures in the MPa range, be reasonably predicted with the homogeneous shrinking assumption, or similar refinements thereof. Such schemes nevertheless require rather detailed statistical knowledge of local particle configurations. On the other hand, the shear response of low coordination packings, such as C and D, is better described with reference to a state with no force indeterminacy, even though hyperstaticity is not observed to vanish in slowly assembled packings under low pressures, except for unphysically large friction coefficients (as in the Z configuration series). In the rigid, $\kappa \rightarrow \infty$ limit, shear moduli become proportional to the level of force indeterminacy, which directly relates to $z^* - 4$, with a small correction due to divalent particles. The dependence of $z^* - 4$ on pressure seems however difficult to predict with the necessary accuracy. The phenomena ruling the departure from linear elastic response are correlated with z^* as well. The failure of elasticity and reversibility appears considerably later, in terms of relative stress increments, for isotropic pressure changes, and, to a lesser extent, in high coordination packings subjected to deviatoric stress paths. In such cases linear elasticity fails because of frictional forces. Elasticity ceases to apply for very small shear stress increments in low coordination

systems, the smaller the closer they are to packings devoid of force indeterminacy. In such cases the predictions of elasticity also fail because of network fragility, as the contact structure breaks apart in response to stress increases. Extension of linear elastic régimes observed in numerical simulations agree semi-quantitatively with observations on sands. The shape of the stress-strain curves beyond the elastic range correlates with the coordination number, with a much stiffer response in well coordinated packings. On comparing numerical and experimental results, the low pressure régime of poorly coordinated networks corresponds to the lowest pressures for which laboratory results are available. The characteristic features of this régime, such as G increasing with P faster than B , or V_S faster than V_P , are not observed in the data we have reported here on dense samples, from the experiments of Jia and Mills [22, 24]. Yet some observations made by Kuwano and Jardine on looser sphere packings [6] show similar trends to C and D-state simulations.

The variety of observations corresponding to the same pressure and density values for the same material confirms the sensitivity of elastic moduli to otherwise undetectable differences in inner structures. It seems in particular, although information about the full stress tensor in the measurements of [22, 24] is lacking, that packings densified by vibrations or repeated shakes have a smaller coordination number than lubricated ones, in spite of a possibly larger density. Additional experimental results with more detailed information on stresses and anisotropy of elastic moduli in packings assembled by different procedures, as well as simulations of anisotropic packings, could enable more quantitative comparisons.

Based on those results, several interesting perspectives should be pursued in the near future.

On the theoretical side, it seems promising to study how granular packings, within and outside the elastic range, deform and destabilize, in more microscopic detail. Basically, packings with few contacts are closer to failure, and some of their anomalies in elastic properties correlate with failure mechanisms. Amorphous systems made of model atoms or molecules at zero temperature have been characterized, in this respect, in terms of an intrinsic scale [60, 61], and elementary plastic rearrangement events, the spatial structure of which is similar to that of nonaffine elastic displacements, have been investigated [62]. Granular materials have friction, which requires more sophisticated stability analyses of given contact networks [55, 63, 64, 65], interact with much stiffer force laws, and exhibit characteristic dilatancy properties and fabric evolutions under strain. It is worth investigating in greater detail the possible similarities and differences between their quasistatic rheology and the plasticity of amorphous materials. Characteristic length scales have also been invoked in relation with the singular elastic properties of frictionless packings [49], which diverge in the isostatic limit. It should be examined whether such a length plays a role in nonelastic deformation behaviors, and similar investigations should be carried out in

systems with friction, which also exhibit complex, long-range correlated strain fields [66].

More practical issues which deserve investigations are how elastic moduli, which can be measured in equilibrated packings under varying stresses [17], can be used to infer useful information on their inner structure, which, in turn, can be exploited to predict their behavior under larger disturbances. As an example, the coordination number of an isotropic packing, if it is large, will result in a stiff response to deviator stress increments, characteristic of a stable contact network (see Fig. 18 and Ref. [54]). Numerical simulations of anisotropic stress and fabric states, of stress paths and large strains, and further numerically based correlations between elastic properties and stresses, strains and inner structures are of course necessary. Finally, the geometry of polydisperse and non-spherical particles should also be explored. Such packings might have large populations of rattlers, some more collective stable floppy modes than in the case of spheres [67], and different mechanical properties [68].

APPENDIX A: TANGENTIAL ELASTICITY AND FRICTION

We investigate here the effect on elastic moduli of the corrections to the contact law advocated in [69] that we adopted in our simulations, and we also discuss the possible effects of more sophisticated models, in which the partial mobilization of friction and the presence of a sliding region within the contact area [35, 70] is taken into account.

Strictly speaking, those terms preclude the definition of a perfectly elastic response, which should be reversible and involve a uniquely defined stiffness matrix.

The simplified law we adopted involves a tangential stiffness K_T depending on the normal deflection h , but independent of the current mobilization of friction. This is the same approximation as used in [8, 12]: the value of K_T is the correct one in the absence of elastic relative tangential displacement, when $\mathbf{T} = 0$.

The rescaling of K_T we chose to apply in situations of decreasing normal force N , in order to avoid energetic inconsistencies, as explained in paper I [1], means that the contact stiffness matrix, as written in Section II B, should be written differently in those case. Specifically, its block corresponding to contact i, j should be $\underline{\underline{K}}_{ij}^E$, as written in (6), if N_{ij} (or, equivalently, h_{ij}) is increasing, but should take another form $\underline{\underline{K}}_{ij}^R$ for a receding pair. Since K_T/K_N is constant, and $K_N \propto N^{1/3}$, one has then, with \mathbf{n}_{ij} and $\mathbf{T}_{ij}/\|\mathbf{T}_{ij}\|$ as first and second basis vectors,

$$\underline{\underline{K}}_{ij}^R = \begin{bmatrix} K_N(h_{ij}) & 0 & 0 \\ \frac{\|\mathbf{T}_{ij}\|}{3N_{ij}} K_N(h_{ij}) & K_T(h_{ij}) & 0 \\ 0 & 0 & K_T(h_{ij}) \end{bmatrix}. \quad (\text{A1})$$

The non-diagonal element of (A1) is smaller than $(\mu/3)K_N(h)$ ($K_N/10$ for $\mu = 0.3$), and its effects are likely limited if friction is not too strongly mobilized, as should be the case under isotropic loads. Let us denote as $\underline{\underline{\mathbf{K}}}$ the correction to the symmetric form of stiffness matrix $\underline{\underline{\mathbf{K}}}^{(1)} \simeq \underline{\underline{\mathbf{K}}}$ (see Section II B), in which Eqn. (6) is applied to all contacts, due to this treatment of decreasing normal forces. We solved the linear system of equations (13), with loads corresponding to different global stress increments, to first order in the perturbation $\Delta\underline{\underline{\mathbf{K}}}$:

$$\mathbf{U} \simeq \mathbf{U}^{(0)} + \Delta\mathbf{U},$$

where $\mathbf{U}^{(0)}$ is the solution to the unperturbed problem, $\mathbf{U}^{(0)} = \underline{\underline{\mathbf{K}}}^{-1} \cdot \mathbf{F}^{\text{ext}}$, and $\Delta\mathbf{U}$ is the correction:

$$\Delta\mathbf{U} = -\underline{\underline{\mathbf{K}}}^{-1} \cdot \Delta\underline{\underline{\mathbf{K}}} \cdot \mathbf{U}^{(0)}. \quad (\text{A2})$$

In (A2) one should pay attention to the directional dependence of $\Delta\underline{\underline{\mathbf{K}}}$ (according to whether h increases or decreases). The first-order correction is therefore not linear, but depends linearly on the amplitude of load increment with a coefficient depending on its direction. We evaluated the resulting correction to the compliance in the cases of uniaxial (*e.g.*, $\Delta\sigma_1 > 0$ or $\Delta\sigma_1 < 0$ while $\Delta\sigma_2 = \Delta\sigma_3 = 0$), isotropic (positive or negative value of $\Delta\sigma_1 = \Delta\sigma_2 = \Delta\sigma_3$) and purely deviatoric (*e.g.*, $\Delta\sigma_1 = -\Delta\sigma_2$ and $\Delta\sigma_3 = 0$) stress increments. Relative corrections never exceeded 1%, the largest ones, as expected, being observed for an isotropic pressure *reduction* (which tends to reduce normal contact forces).

Our contact model also introduces an approximation, which we now discuss. A more sophisticated version of the contact law, as used by some authors [10, 71] would keep track of part of the slip distribution within the contact region. The *maximum* effect of such slip is to *reduce* the tangential stiffness from $K_T(N)$, its value for $\mathbf{T} = 0$, to

$$K'_T(N, \mathbf{T}) = K_T(N) \left(1 - \frac{\|\mathbf{T}\|}{N}\right)^{1/3}. \quad (\text{A3})$$

in the “loading” direction (*i.e.*, tending to increase $\|\mathbf{T}\|/N$), and for the tangential relative displacements along \mathbf{T} . In order to assess the possible influence on the simulated elastic properties of our overestimating the tangential stiffness of the contacts, we computed the elastic moduli for the equilibrated configurations, keeping the same values of contacts forces, using formula A3 for all contacts, in both tangential directions (such a calculation thus implicitly assumes that the force distribution is not affected by the change in the contact law). It should be emphasized that it exaggerates the effects of slip and gradual friction mobilization, as formula A3 gives the lowest possible value for K_T and only applies in specific loading histories, and for stress increments that tend to increase $\frac{\|\mathbf{T}\|}{N}$. Relative corrections to computed elastic moduli evaluated with this procedure never exceed 3%.

Consequently, it is a very good approximation to replace the contact stiffness matrix $\underline{\underline{\mathbf{K}}}$ by its diagonal form

given by Eqn. (6), provided friction is not fully mobilized in any contact.

If condition $\|\mathbf{T}\| = \mu N$ is reached in contact i, j , then matrix $\underline{\underline{\mathbf{K}}}_{ij}$ has to be written as follows. With the same choice of basis vectors as for (A1), $\underline{\underline{\mathbf{K}}}_{ij}$ has a “loading” form $\underline{\underline{\mathbf{K}}}_{ij}^L$ given by

$$\underline{\underline{\mathbf{K}}}_{ij}^L = \begin{bmatrix} K_N(h_{ij}) & 0 & 0 \\ \mu K_N(h_{ij}) & 0 & 0 \\ 0 & 0 & K_T(h_{ij}) \end{bmatrix} \quad (\text{A4})$$

and an “unloading” one equal to $\underline{\underline{\mathbf{K}}}_{ij}^E$ or to $\underline{\underline{\mathbf{K}}}_{ij}^R$, depending on whether δu_N is increasing or decreasing. If it is increasing, the loading form $\underline{\underline{\mathbf{K}}}_{ij}^L$ should be used if

$$K_T(h_{ij})\delta\mathbf{u}_{ij}^T \cdot \frac{\mathbf{T}_{ij}}{\|\mathbf{T}_{ij}\|} - \mu K_N(h_{ij})\delta\mathbf{u}_{ij}^N > 0.$$

If δu_N is decreasing, this condition becomes

$$K_T(h_{ij})\delta\mathbf{u}_{ij}^T \cdot \frac{\mathbf{T}_{ij}}{\|\mathbf{T}_{ij}\|} + \left[\frac{\|\mathbf{T}_{ij}\|}{3N_{ij}} - \mu \right] K_N(h_{ij})\delta\mathbf{u}_{ij}^N > 0.$$

Note that $\underline{\underline{\mathbf{K}}}_{ij}^L$ is a non-symmetric singular matrix of rank 2. As remarked in Section II C, well-equilibrated configurations prepared by molecular dynamics do not contain any contact where the condition $\|\mathbf{T}\| = \mu N$ is exactly reached.

APPENDIX B: GEOMETRIC STIFFNESS MATRIX

The geometric term added to the change in intergranular forces entailed by small displacements and rotations was evaluated in paper I [1]. Here, for completeness, we write down its contribution to the geometric stiffness matrix $\underline{\underline{\mathbf{K}}}^{(2)}$. Those terms stem from the change in the direction of previous contact forces. They were carefully evaluated in general situations of particles of arbitrary shapes by Kuhn and Chang [63], and by Bagi [64]. Our results agree with the general expressions written down in those references, in the simple case of spherical grains. The radii of the spheres is simply denoted as R_i below (in our numerical computations, all R_i values are equal to $a/2$). In the general case of arbitrary-shaped grains, both “branch vectors”, joining contact points to particle centers where moments are evaluated, and particle surface curvatures, which determine the small changes in normal directions, affect the results. With spheres, both quantities simply relate to the radii.

The 6×6 block $\underline{\underline{\mathbf{K}}}_{ij}^{(2)}$ of the geometric stiffness matrix is a sum over the contacts of grain i ,

$$\underline{\underline{\mathbf{K}}}_{ii}^{(2)} = \sum_{j \neq i} \underline{\underline{\mathbf{L}}}_{ij},$$

each term being given by the expressions written in paper I [1, appendix B]. Using a system of coordinates with \mathbf{n}_{ij} and \mathbf{T}_{ij} setting the orientations of the two first axes, one has:

$$\underline{\underline{\mathbf{L}}}_{ij} = \begin{bmatrix} 0 & \frac{T_{ij}}{r_{ij}} & 0 & 0 & 0 & 0 \\ 0 & -\frac{N_{ij}}{r_{ij}} & 0 & 0 & 0 & 0 \\ 0 & 0 & -\frac{N_{ij}}{r_{ij}} & \frac{T_{ij}}{2} & 0 & 0 \\ 0 & 0 & 0 & 0 & 0 & 0 \\ 0 & 0 & \frac{N_{ij}R_i}{r_{ij}} & -\frac{R_iT_{ij}}{2} & 0 & 0 \\ 0 & -\frac{N_{ij}R_i}{r_{ij}} & 0 & 0 & 0 & 0 \end{bmatrix} \quad (\text{B1})$$

As to the non-diagonal block $\underline{\underline{\mathbf{K}}}_{ij}^{(2)}$, it is obtained from $\underline{\underline{\mathbf{L}}}_{ij}$ on reversing the signs of the coefficients in the three first columns. Diagonal blocks of $\underline{\underline{\mathbf{K}}}^{(2)}$ are therefore clearly not symmetric, which, in principle, forbids the definition of an elastic energy. However, each term involving N_{ij} or t_{ij} in $\underline{\underline{\mathbf{K}}}^{(2)}$ is negligible once compared to its counterpart in $\underline{\underline{\mathbf{K}}}^{(1)}$, where it is replaced by terms of order $K_N a$. Generally, $\underline{\underline{\mathbf{K}}}^{(2)}$ terms are of relative order κ^{-1} if compared to the corresponding ones in $\underline{\underline{\mathbf{K}}}^{(1)}$. Thus the geometric stiffness matrix only plays a role for those directions of displacement vectors belonging to the null space of $\underline{\underline{\mathbf{K}}}^{(1)}$. This is important for frictionless grains, in which case such floppy modes of the constitutive matrix are necessarily unstable for spheres, but not so for, *e.g.*, ellipsoids [32, 67]. In the case of frictional spheres we did not obtain any floppy mode on the backbone, except for beads with two contacts. However, the corresponding free motion turns out to belong to the null space of $\underline{\underline{\mathbf{K}}}^{(2)}$ as well in that case [1].

We can therefore safely neglect the geometric part of the stiffness matrix in all cases studied in the present numerical work.

APPENDIX C: ELASTICITY OF A PRESTRESSED SYSTEM

We first deal with an elastic continuum, and recall here some basic properties which lead to a distinction to be made, when the reference configuration is prestressed, between the elastic moduli and the coefficients of the linear relation between the Cauchy stress tensor and the strains. Then, returning to our discrete simulations, we discuss some (small) corrections to be made to our computed elastic moduli, due to the role of preexisting stresses.

We first consider a uniform displacement gradient $\nabla \mathbf{u}$ within an elastic continuous medium (derivatives with respect to coordinates on the reference, undisturbed configuration). For general displacement fields, the relations

written below apply locally. Linear elasticity assumes that the free energy density, A/Ω_0 , evaluated in a reference configuration (with volume Ω_0), is a quadratic function of the Green-Lagrange strain tensor $\underline{\underline{\mathbf{e}}}$, which expresses material deformation. The first-order term is written with the Piola-Kirchoff stress tensor in the reference configuration, $\underline{\underline{\pi}}_0$,

$$\mathcal{P} = \Omega_0 \underline{\underline{\pi}}_0 : \underline{\underline{\mathbf{e}}}. \quad (\text{C1})$$

(The Piola-Kirchoff stress tensor relates to the Cauchy stress tensor $\underline{\underline{\sigma}}$ as

$$\underline{\underline{\pi}} = \frac{\Omega}{\Omega_0} \underline{\underline{\mathbf{L}}}_0 \cdot \underline{\underline{\mathbf{L}}}^{-1} \cdot \underline{\underline{\Sigma}} \cdot \mathbf{T} \underline{\underline{\mathbf{L}}}^{-1} \cdot \mathbf{T} \underline{\underline{\mathbf{L}}}_0^{-1}, \quad (\text{C2})$$

as recalled in paper I. In this expression, $\underline{\underline{\mathbf{L}}}$ is the diagonal matrix containing the cell dimensions along the three axes, and $\underline{\underline{\mathbf{L}}}_0$ denotes its value in the reference configuration). To second order, the free energy associated with small strains involves the tensor of elastic constants $\underline{\underline{\underline{\mathbf{C}}}}$:

$$A = \Omega_0 \left[\underline{\underline{\pi}}_0 : \underline{\underline{\mathbf{e}}} + \frac{1}{2} \underline{\underline{\mathbf{e}}} : \underline{\underline{\underline{\mathbf{C}}}} : \underline{\underline{\mathbf{e}}} \right]. \quad (\text{C3})$$

Elastic moduli thus appear in the increment of $\underline{\underline{\pi}}$:

$$\underline{\underline{\pi}} - \underline{\underline{\pi}}_0 = \underline{\underline{\underline{\mathbf{C}}}} : \underline{\underline{\mathbf{e}}}. \quad (\text{C4})$$

The Voigt symmetry $C_{\alpha\beta\gamma\delta} = C_{\gamma\delta\alpha\beta}$, eqn. C4, is satisfied by the coefficients of the linear law because those are second order derivatives. Introducing the notation $\underline{\underline{\mathbf{F}}} = \underline{\underline{\mathbf{1}}} + \nabla \mathbf{u}$ (one has $\underline{\underline{\mathbf{F}}} = \underline{\underline{\mathbf{L}}} \cdot \underline{\underline{\mathbf{L}}}_0^{-1}$ in the context of the simulation technique with a deformable cell we are using in the present study (see paper I), one has $\Omega/\Omega_0 = \det \underline{\underline{\mathbf{F}}}$ for the dilation and $\underline{\underline{\sigma}}$ is related to $\underline{\underline{\pi}}$ by Eqn. C2 or

$$\underline{\underline{\pi}} = (\det \underline{\underline{\mathbf{F}}}) \underline{\underline{\mathbf{F}}}^{-1} \cdot \underline{\underline{\sigma}} \cdot \mathbf{T} \underline{\underline{\mathbf{F}}}^{-1}. \quad (\text{C5})$$

To establish (C5), one needs just recall that the power of internal forces in any motion with uniform Eulerian strain rate tensor $\underline{\underline{\mathbf{D}}}$ is

$$\mathcal{P}' = \Omega \underline{\underline{\sigma}} : \underline{\underline{\mathbf{D}}}. \quad (\text{C6})$$

$\underline{\underline{\mathbf{D}}}$ is the opposite of the symmetric part of the Eulerian velocity gradient tensor (with our sign convention)

$$D_{\alpha\beta} = -\frac{1}{2} \left(\frac{\partial v_\alpha}{\partial x_\beta} + \frac{\partial v_\beta}{\partial x_\alpha} \right).$$

x_α are here the coordinates in the deformed system, and derivatives with respect to the coordinates X_α of the same point in the reference configuration are such that

$$\frac{\partial}{\partial X_\beta} = \sum_\alpha \frac{\partial}{\partial x_\alpha} \cdot F_{\alpha\beta}. \quad (\text{C7})$$

Hence the relation between $\underline{\underline{\mathbf{D}}}$ and $\underline{\underline{\dot{\mathbf{e}}}}$:

$$\underline{\underline{\mathbf{D}}} = \mathbf{T} \underline{\underline{\mathbf{F}}}^{-1} \cdot \underline{\underline{\dot{\mathbf{e}}}} \cdot \underline{\underline{\mathbf{F}}}^{-1}.$$

Using this relation, and equating \mathcal{P} (C1) and \mathcal{P}' (C6), for any uniform velocity gradient, one readily derives relation (C5).

Let us now use (C4) and (C5) to write the increment of the Cauchy stress tensor to first order in displacement gradient $\underline{\underline{\nabla\mathbf{u}}}$ (needless to distinguish spatial derivatives in the reference or the deformed configuration at this stage, as (C7) would introduce second order corrections). Defining the linearized strain tensor $\underline{\underline{\epsilon}}$ as

$$\underline{\underline{\epsilon}} = -\frac{1}{2} (\underline{\underline{\nabla\mathbf{u}}} + \mathbf{T}\underline{\underline{\nabla\mathbf{u}}}),$$

one obtains:

$$\underline{\underline{\sigma}} = \underline{\underline{\pi}}_0 - (\text{tr}\underline{\underline{\epsilon}}) \underline{\underline{\pi}}_0 - \underline{\underline{\nabla\mathbf{u}}} \cdot \underline{\underline{\pi}}_0 - \underline{\underline{\pi}}_0 \cdot \mathbf{T}\underline{\underline{\nabla\mathbf{u}}} + \underline{\underline{\mathbf{C}}} : \underline{\underline{\epsilon}}. \quad (\text{C8})$$

Therefore, $\underline{\underline{\sigma}}$ is not necessarily a function of the symmetric part of $\underline{\underline{\nabla\mathbf{u}}}$ only. A rigid rotation (for which $\underline{\underline{\nabla\mathbf{u}}}$ is antisymmetric) might produce a Cauchy stress increment if $\underline{\underline{\pi}}_0$ and $\underline{\underline{\nabla\mathbf{u}}}$ do not commute. Likewise, the coefficients expressing the linear dependence of $\underline{\underline{\sigma}}$ on $\underline{\underline{\nabla\mathbf{u}}}$ do not always satisfy the Voigt symmetry, and hence one cannot regard a constant $\underline{\underline{\sigma}}$ as deriving from a potential energy of external loading. Both conditions (symmetry and dependence on $\underline{\underline{\epsilon}}$ only) are however restored if one restricts to symmetric displacement gradients, or if $\underline{\underline{\pi}}$ and $\underline{\underline{\epsilon}}$ share common principal directions (which is always the case with our choice of boundary conditions), or of course if $\underline{\underline{\pi}}_0 = P\underline{\underline{\mathbf{1}}}$ is an isotropic tensor. In this latter case, (C8) relates $\underline{\underline{\sigma}}$ to $\underline{\underline{\epsilon}}$, assuming isotropy of the material, with a tensor of ‘‘apparent’’ elastic moduli $\underline{\underline{\mathbf{B}}}$, that has the same symmetries as $\underline{\underline{\mathbf{C}}}$. $\underline{\underline{\mathbf{C}}}$, in isotropic systems, can be written with a bulk modulus B and a shear modulus G . On relating $\underline{\underline{\sigma}}$ to $\underline{\underline{\epsilon}}$, the apparent moduli (as measured in an experiment) are $B + P/3$ and $G - P$.

Returning now to the isotropic sphere packings we studied by numerical simulations, it should be specified that our procedure to compute elastic moduli is based on a formula for the Cauchy stress tensor, and therefore the resulting moduli are the elements of matrix $\underline{\underline{\mathbf{B}}}$, rather than $\underline{\underline{\mathbf{C}}}$. Then, as a consequence of the stress and forces that preexist in the initial configuration before elastic response is probed, our results should also in principle be slightly modified. (12) actually gives the increment of the product $\Omega\sigma_\alpha$, from which the contribution $\Delta\Omega\sigma_\alpha^0$, due to volume change $\Delta\Omega = -\Omega_0\text{tr}\underline{\underline{\epsilon}}$ should be subtracted before dividing by Ω_0 if the stress variation is to be obtained. As a consequence of this correction, we should in principle add $P/3$ to the value of B obtained with our calculation procedure. This is a small effect, similar to that of matrix $\underline{\underline{\mathbf{K}}}^{(2)}$, which we have been neglecting (moduli of the order of 100 MPa for $P \sim 100$ kPa).

APPENDIX D: VOIGT AND REUSS BOUNDS FOR ELASTIC MODULI IN A SPHERE PACKING

Within the approximation that the stiffness matrix does not depend on the direction of the stress (or strain) increment, and is symmetric (see Section II C and Appendix A), which fortunately proves accurate (see also Section VII), the elastic régime can be defined, and the variational properties (15) and (16) can be used. Variational properties leading to bounds for moduli are seldom invoked in the context of granular materials. Our purpose here is to recall how these useful properties are established and interrelated, and how they can be exploited. Specifically, we now proceed to

- state variational properties in both stress-controlled and strain-controlled cases;
- check the equivalence of the two approaches;
- establish the less familiar minimization property for contact force increments;
- derive the expressions (26), (27) of the bounds for B and G in the isotropic case.

Variational properties take different forms according to whether stress increments or strain increments are controlled. The forms corresponding to controlled stress increments were stated in connection with (15) and (16).

If strains $\underline{\underline{\epsilon}}$ are imposed, then displacement vector \mathbf{U} , which is constrained to correspond to $\underline{\underline{\epsilon}}$ (this sets the values of its three last coordinates with our choice of boundary conditions) should minimize:

$$\mathcal{E}_1(\mathbf{U}) = \frac{1}{2} \mathbf{U} \cdot \underline{\underline{\mathbf{K}}} \cdot \mathbf{U} \quad (\text{D1})$$

while the contact force increments, vector $\Delta\mathbf{f}$, should equilibrate each grain and minimize

$$\mathcal{E}_2(\Delta\mathbf{f}) = \frac{1}{2} \Delta\mathbf{f} \cdot \underline{\underline{\mathbf{K}}}^{-1} \cdot \Delta\mathbf{f} - \Omega \Delta\underline{\underline{\sigma}} : \underline{\underline{\epsilon}}, \quad (\text{D2})$$

in which the stress increment $\underline{\underline{\Delta\sigma}}$ is directly given by $\Delta\mathbf{f}$, just like stress components relate to contact forces in (12).

Minimum values in (15) and (16) are

$$W_1^* = -\frac{\Omega_0}{2} \Delta\underline{\underline{\sigma}} : \underline{\underline{\mathbf{C}}}^{-1} : \Delta\underline{\underline{\sigma}}$$

$$W_2^* = -W_1^*$$

in the stress-controlled case, when $\underline{\underline{\Delta\sigma}}$ is imposed. The values obtained with trial solutions for displacements or contact force increments can then be regarded as estimates of those quadratic expressions in $\underline{\underline{\Delta\sigma}}$, and hence provide estimates of the corresponding compliance matrix $\underline{\underline{\mathbf{C}}}^{-1}$. The meaning of $\underline{\underline{\mathbf{C}}}^{-1}$, in a finite sample, is specific to the choice of particular boundary conditions.

In the large sample limit, it is assumed to satisfy the symmetry properties of the medium, which is statistically isotropic in the numerical studies reported here. Moreover, it is also expected to approach the macroscopic compliance matrix, whatever the particular choice of boundary conditions. If, as in our numerical study, we restrict $\underline{\underline{\sigma}}$ to a diagonal form, and hence regard it as a vector with three coordinates σ_α , $\alpha = 1, 2, 3$, $\underline{\underline{\mathbf{C}}}^{-1}$ is a matrix $\underline{\underline{\mathbf{S}}}$ of the form

$$\underline{\underline{\mathbf{S}}} = \begin{bmatrix} S_{11} & S_{12} & S_{12} \\ S_{12} & S_{11} & S_{12} \\ S_{12} & S_{12} & S_{11} \end{bmatrix} \quad (\text{D3})$$

with, due to isotropy,

$$S_{11} = \frac{1}{9B} + \frac{1}{3G}$$

$$S_{12} = \frac{1}{9B} - \frac{1}{6G}.$$

When $\underline{\underline{\Delta\sigma}}$ is an isotropic pressure increment ΔP , one has

$$W_2^* = -W_1^* = \frac{\Omega_0(\Delta P)^2}{3B},$$

whence an upper bound to B with an estimate of W_1^* , and a lower bound with an estimate of W_2^* .

When $\underline{\underline{\Delta\sigma}}$ is of the form $(q, -q, 0)$, then

$$W_2^* = -W_1^* = \frac{\Omega_0 q^2}{2G}, \quad (\text{D4})$$

whence an upper bound to G with an estimate of W_1^* , and a lower bound with an estimate of W_2^* .

Minimum values in (D1) and (D2) are

$$\mathcal{E}_1^* = \frac{\Omega_0}{2} \underline{\underline{\epsilon}} : \underline{\underline{\mathbf{C}}} : \underline{\underline{\epsilon}}$$

$$\mathcal{E}_2^* = -\mathcal{E}_1^*$$

in the strain-controlled case, when $\underline{\underline{\epsilon}}$ is imposed. The values obtained with trial solutions for displacements or contact force increments can then be regarded as estimates of those quadratic expressions in $\underline{\underline{\epsilon}}$, and hence provide estimates of the corresponding stiffness matrix $\underline{\underline{\mathbf{C}}}$. The meaning of $\underline{\underline{\mathbf{C}}}$, in a finite sample, is specific to the choice of particular boundary conditions. In the large sample limit, it is assumed to satisfy the symmetry properties of the medium, which is statistically isotropic in the numerical studies reported here. Moreover, it is also expected to approach the macroscopic stiffness matrix, whatever the particular choice of boundary conditions. If, as in our numerical study, we restrict $\underline{\underline{\epsilon}}$ to a diagonal form, and hence regard it as a vector with three coordinates ϵ_α , ($\alpha = 1, 2, 3$), $\underline{\underline{\mathbf{C}}}$ can be written as a matrix $\underline{\underline{\mathbf{C}}}$ of the form

$$\underline{\underline{\mathbf{C}}} = \begin{bmatrix} C_{11} & C_{12} & C_{12} \\ C_{12} & C_{11} & C_{12} \\ C_{12} & C_{12} & C_{11} \end{bmatrix} = \underline{\underline{\mathbf{S}}}^{-1}, \quad (\text{D5})$$

with, due to isotropy,

$$C_{11} = B + \frac{4}{3}G$$

$$C_{12} = B - \frac{2}{3}G.$$

When $\underline{\underline{\epsilon}}$ is an isotropic shrinking strain of the form $(\epsilon, \epsilon, \epsilon)$, one has

$$\mathcal{E}_1^* = -\mathcal{E}_2^* = \frac{9\Omega_0 B \epsilon^2}{2},$$

whence an upper bound to B with an estimate of \mathcal{E}_1^* , and a lower bound with an estimate of \mathcal{E}_2^* .

When $\underline{\underline{\epsilon}}$ is of the form $(\lambda, -\lambda, 0)$, then

$$\mathcal{E}_1^* = -\mathcal{E}_2^* = 2\Omega_0 G \lambda^2,$$

whence an upper bound to G with an estimate of \mathcal{E}_1^* , and a lower bound with an estimate of \mathcal{E}_2^* .

Let us now show that the same form of trial displacements lead to the same estimates of matrices $\underline{\underline{\mathbf{C}}}$ and $\underline{\underline{\mathbf{S}}}$ in the strain-controlled and stress-controlled approaches. We restrict $\underline{\underline{\epsilon}}$ and $\underline{\underline{\Delta\sigma}}$ to 3-vectors, like in our calculations, respectively denoted as $\vec{\epsilon}$ and $\vec{\sigma}$, but we do not immediately assume isotropy. Let us define trial displacements of the following form: for each grain i ,

$$\mathbf{u}_i = -\underline{\underline{\epsilon}} \cdot \mathbf{R}_i$$

$$\delta\theta_i = \vec{\omega}, \quad (\text{D6})$$

i.e., we assume an affine displacement field, $\tilde{\mathbf{u}}_i = 0$ in (7), and attribute to each grain the same spin $\vec{\omega}$.

In the strain-controlled approach, the three coordinates of $\underline{\underline{\epsilon}}$ are given, while the optimal value of ω is the one minimizing function \mathcal{E}_1 restricted to displacement vectors of the form (D6), which is necessarily a quadratic form:

$$\mathcal{E}_1(\vec{\epsilon}, \vec{\omega}) = \frac{\Omega_0}{2} [\vec{\epsilon} \cdot \underline{\underline{\mathbf{L}}} \cdot \vec{\epsilon} + 2\vec{\epsilon} \cdot \underline{\underline{\mathbf{M}}} \cdot \vec{\omega} + \vec{\omega} \cdot \underline{\underline{\mathbf{N}}} \cdot \vec{\omega}].$$

$\underline{\underline{\mathbf{L}}}$, $\underline{\underline{\mathbf{M}}}$, and $\underline{\underline{\mathbf{N}}}$ are 3×3 matrices such that the quadratic form is positive definite, and can be evaluated, as we shall see, as averages over contacts. Minimization of $\mathcal{E}_1(\vec{\epsilon})$ leads to the optimal choice $\vec{\omega}^*$ for the spin:

$$\vec{\omega}^* = -\underline{\underline{\mathbf{N}}}^{-1} \cdot \underline{\underline{\mathbf{T}}}\underline{\underline{\mathbf{M}}} \cdot \vec{\epsilon}, \quad (\text{D7})$$

whence the approximation to \mathcal{E}_1^* in which the exact stiffness matrix $\underline{\underline{\mathbf{C}}}$ is replaced by its estimate:

$$\underline{\underline{\mathbf{C}}}_{\text{strain}}^{\text{Voigt}} = \underline{\underline{\mathbf{L}}} - \underline{\underline{\mathbf{M}}} \cdot \underline{\underline{\mathbf{N}}}^{-1} \cdot \underline{\underline{\mathbf{T}}}\underline{\underline{\mathbf{M}}} \quad (\text{D8})$$

In the stress-controlled approach, one should minimize

$$W_1(\vec{\epsilon}, \vec{\omega}) = \mathcal{E}_1(\vec{\epsilon}, \vec{\omega}) - \Omega_0 \vec{\sigma} \cdot \vec{\epsilon},$$

with respect to both vectors $\vec{\epsilon}$ and $\vec{\omega}$, which results in the best variational estimates:

$$\vec{\omega}^* = -\underline{\underline{\mathbf{N}}}^{-1} \cdot \underline{\underline{\mathbf{T}}}\underline{\underline{\mathbf{M}}} \cdot \vec{\epsilon}$$

$$\vec{\epsilon}^* = (\underline{\underline{\mathbf{L}}} - \underline{\underline{\mathbf{M}}} \cdot \underline{\underline{\mathbf{N}}}^{-1} \cdot \underline{\underline{\mathbf{T}}}\underline{\underline{\mathbf{M}}})^{-1} \cdot \vec{\sigma} \quad (\text{D9})$$

On estimating the minimum of W_1 , and therefore $\underline{\mathbf{S}} = \underline{\mathbf{C}}^{-1}$, this yields

$$\underline{\mathbf{S}}_{\text{stress}}^{\text{Voigt}} = (\underline{\mathbf{L}} - \underline{\mathbf{M}} \cdot \underline{\mathbf{N}}^{-1} \cdot \mathbf{T}\underline{\mathbf{M}})^{-1} \quad (\text{D10})$$

Eqns. D8 and D10 show that both the strain-controlled and the stress-controlled approaches yield the same results, sample by sample, for the Voigt type estimation of elastic moduli, based on a trial displacement field. As we did not write down the exact form of the matrices yet, the same conclusions would have been reached for whatever form of a trial displacement vector expressed as a linear combination of a set of parameters.

Similar conclusions are easily reached for the other two, Reuss-type, variational properties, based on trial contact force increments, involving (16) and (D2).

Let us now write down matrices $\underline{\mathbf{L}}$, $\underline{\mathbf{M}}$, and $\underline{\mathbf{N}}$ in a sphere packing with our boundary conditions. Let us introduce the notations

$$\begin{aligned} L_{ij}^N &= (R_i + R_j)^2 K_{ij}^N \\ L_{ij}^T &= (R_i + R_j)^2 K_{ij}^T \end{aligned}$$

for each contact i, j between spheres of radii R_i and R_j , and neglect h_{ij} in comparison with the radii, as we have been doing throughout this article. Then one has, for each pair of indices α, β , $1 \leq \alpha, \beta \leq 3$,

$$\begin{aligned} L_{\alpha\beta} &= \frac{1}{\Omega_0} \sum_{i<j} \left[L_{ij}^N (n_{ij}^\alpha)^2 (n_{ij}^\beta)^2 + L_{ij}^T (\delta_{\alpha\beta} - n_{ij}^\alpha n_{ij}^\beta) n_{ij}^\alpha n_{ij}^\beta \right] \\ M_{\alpha\beta} &= \frac{1}{\Omega_0} \sum_{i<j} L_{ij}^T \epsilon_{\alpha\delta\beta} n_{ij}^\gamma (n_{ij}^\alpha \delta_{\alpha\delta} - (n_{ij}^\alpha)^2 n_{ij}^\delta) \\ N_{\alpha\beta} &= \frac{1}{\Omega_0} \sum_{i<j} L_{ij}^T (\delta_{\alpha\beta} - n_{ij}^\alpha n_{ij}^\beta) n_{ij}^\alpha n_{ij}^\beta \end{aligned} \quad (\text{D11})$$

In (D11), sums over repeated Greek indices different from α and β are implied, $\delta_{\alpha\beta}$ is the Kronecker symbol and $\epsilon_{\alpha\beta\gamma}$ is the Levi-Civittà symbol, expressing the coordinates of a vector product, and index pairs $i < j$ run over the list of force-carrying contacts between grains labelled i and j .

An alternative expression of matrix $\underline{\mathbf{M}}$ is, square brackets denoting a matrix commutator,

$$\mathbf{T}\underline{\mathbf{M}} \cdot \vec{\epsilon} = \left[\frac{1}{\Omega_0} \sum_{i<j} (L_{ij}^T \mathbf{n}_{ij} \otimes \mathbf{n}_{ij}), \underline{\underline{\epsilon}} \right] \quad (\text{D12})$$

This shows that the best estimate $\vec{\omega}^*$ obtained in (D7) for the rotation vector applied to all grains is equal to zero if the strain tensor and the symmetric fabric tensor defined as the average of $\mathbf{n}_{ij} \otimes \mathbf{n}_{ij}$ over contacts, weighted by L_{ij}^T , share the same eigenvectors. In such cases, $\underline{\mathbf{M}} = 0$. This conclusion, which was reached before by Jenkins and La Ragione [72], and independently by Gay and da Silveira [73], on directly estimating the stress increments

corresponding to a prescribed strain, is retrieved here as an illustration of the variational approach.

Returning now to the case of isotropic packings of monodisperse spherical beads of diameter a , the fabric tensor is isotropic and the commutator vanishes in (D12), and matrix $\underline{\mathbf{L}}$ is the Voigt estimate of $\underline{\mathbf{C}}$. To compute its terms in the large system limit in isotropic packings, we use averages over contacts, defined as

$$\langle X \rangle = \frac{1}{N_c} \sum_{i<j} X_{ij}$$

for any quantity X associated with contacts, and we transform the sums in (D11) using

$$\frac{N_C}{\Omega_0} = \frac{3z\Phi}{\pi a^3}.$$

Isotropy also ensures independence between stiffness fluctuations and contact orientations, so that one has, *e.g.*, for any exponents a and b and coordinate indices α, β ,

$$\langle n_\alpha^a n_\beta^b K_N \rangle = \langle n_\alpha^a n_\beta^b \rangle \langle K_N \rangle.$$

Then one has from Eqns. 2 and 3:

$$\langle K_N \rangle = \frac{3^{1/3}}{2} \tilde{E}^{2/3} Z(1/3) \frac{\pi^{1/3} a P^{1/3}}{z^{1/3} \Phi^{1/3}},$$

while $\langle K_T \rangle = \alpha_T \langle K_N \rangle$. Finally, knowing that

$$\langle n_x^4 \rangle = \frac{1}{5} \quad \text{and} \quad \langle n_x^2 n_y^2 \rangle = \frac{1}{15}$$

for isotropically distributed unit vectors, one gets

$$\begin{aligned} C_{11}^{\text{Voigt}} &= \frac{3^{4/3}}{2} \left(\frac{z\Phi\tilde{E}}{\pi} \right)^{2/3} \frac{3 + 2\alpha_T}{15} Z(1/3) P^{1/3} \\ C_{12}^{\text{Voigt}} &= \frac{3^{4/3}}{2} \left(\frac{z\Phi\tilde{E}}{\pi} \right)^{2/3} \frac{1 - \alpha_T}{15} Z(1/3) P^{1/3}, \end{aligned}$$

from which expression (26) of B^{Voigt} and G^{Voigt} is readily derived, since $B = (C_{11} + 2C_{12})/3$ and $G = (C_{11} - C_{12})/2$.

Let us now prove, as announced, the variational property for contact force increments, in the stress-controlled case (the treatment of the strain-controlled approach being similar). We consider the solution $\Delta\mathbf{f}^*$ to the problem of minimizing (16) among contact force increment vectors that balance the applied load increment, *i.e.* such that

$$\mathbf{T}\underline{\underline{\mathbf{G}}} \cdot \Delta\mathbf{f} = \Delta\mathbf{F}^{\text{ext}} \quad (\text{D13})$$

This solution is characterized by the existence of a vector \mathbf{x} of Lagrange multipliers such that

$$\underline{\underline{\mathcal{K}}}^{-1} \cdot \Delta\mathbf{f}^* = \underline{\underline{\mathbf{G}}} \cdot \mathbf{x},$$

and (D13) thus entails

$$\mathbf{T}\underline{\underline{\mathbf{G}}} \cdot \underline{\underline{\mathcal{K}}} \cdot \underline{\underline{\mathbf{G}}} \cdot \mathbf{x} = \underline{\underline{\mathbf{K}}} \cdot \mathbf{x} = \Delta\mathbf{F}^{\text{ext}},$$

This means that \mathbf{x} is the displacement vector solution to the elastic problem, and that $\Delta \mathbf{f}^* = \underline{\underline{K}} \cdot \underline{\underline{G}} \cdot \mathbf{x}$ is indeed the corresponding contact force increment vector.

Finally, to establish the Reuss type lower bound to B , we choose an isotropic stress increment $\Delta \bar{\sigma} = (\Delta P, \Delta P, \Delta P)$ and evaluate W_2 for a trial set of contact force increments chosen, in any sample in equilibrium under pressure P , as

$$\Delta \mathbf{f}_{ij} = \frac{\Delta P}{P} \mathbf{f}_{ij}, \quad (\text{D14})$$

in contact i, j , initially carrying force \mathbf{f}_{ij} . Such force increments balance the load increase ΔP by linearity of equilibrium relation (D13). The resulting value of W_2 ,

$$W_2 = \left(\frac{\Delta P}{P} \right)^2 \frac{1}{2\Omega_0} \sum_{i < j} \frac{N_{ij}^2}{K_{ij}^N} + \frac{\mathbf{T}_{ij}^2}{K_{ij}^T}$$

is quadratic in ΔP , and yields B^{Reuss} , as written in (27), by comparison with (D4), once the sum is transformed by the same procedures as in the case of the Voigt bounds, using the definition of $\tilde{Z}(5/3)$ in (18).

No such trial vector of contact force increments as (D14) is readily available when the applied stress increment is not proportional to the preexisting stress, which is isotropic in the present study. In general, in anisotropic stress states, a similar Reuss-type approach is expected to provide a lower bound estimate for a certain combination of elastic moduli, which expresses the response to proportional load increases.

APPENDIX E: LA RAGIONE-JENKINS ESTIMATES FOR ELASTIC MODULI [44]

The LRJ formulae give bulk and shear moduli proportional to the product Φz , which stems from the evaluation of stresses, and to average stiffnesses $\langle K_N \rangle$ and $\langle K_T \rangle$. The predicted values B^{LRJ} and G^{LRJ} are conveniently written with a factor of B^{Voigt} , as defined in (26). First, let us define Δz_*^2 as the variance of the number of contacts of a backbone grain. Specifically, if x_k , $k = 0, 1, 2, \dots$ denotes the proportion of grains with k force-carrying contacts, one may define

$$x_k^* = \frac{x_k}{1 - x_0}$$

with $k \neq 0$ for the backbone (or non-rattler) grains, so that

$$z^* = \sum_{k \geq 1} k x_k^*,$$

and Δz_*^2 is then given by

$$\Delta z_*^2 = \sum_{k \geq 1} (k - z^*)^2 x_k^*.$$

Then, using notations introduced in [44], we define:

$$\begin{aligned} \rho &= \left(\frac{11}{12} - \frac{z^*}{8} \right) \left(\frac{1}{z^*} - \frac{1}{(z^*)^2} \right) + \frac{\Delta z_*^2}{8(z^*)^2} \\ \xi_5 &= -3 \left(\frac{11}{13} - \frac{3z^*}{26} \right) \left(1 - \frac{24}{13z^*} \right) - \frac{261\Delta z_*^2}{676(z^*)^2} \\ \rho^* &= \rho(1 - 2\rho + 2\xi_5) \\ \xi_5^* &= \xi_5(1 - 2\rho + 2\xi_5), \end{aligned}$$

so that the estimates of the moduli read (let us recall that $\alpha_T = K_T/K_N = 2(1 - \nu)/(2 - \nu)$)

$$\begin{aligned} \frac{B^{LRJ}}{B^{\text{Voigt}}} &= 1 - 2(\rho + \rho^*) \\ \frac{G^{LRJ}}{B^{\text{Voigt}}} &= \frac{3}{5}(1 - \alpha_T)[1 - 2(\rho + \rho^*)] \\ &\quad + \frac{3}{2}\alpha_T \left[1 - 2(\rho + \rho^*) + \frac{6}{5}(\xi_5 + \xi_5^*) \right] \end{aligned} \quad (\text{E1})$$

We observed the ratio $\Delta z_*^2/(z^*)^2$ to depend on both z^* and confining pressure. Under low pressure, typical values are 0.04–0.05 in well-coordinated systems and 0.07–0.08 in poorly coordinated ones. The evolution of Δz_*^2 in a pressure cycle are similar to those of friction mobilization and width of the force distribution reported in paper II [2].

In comparison to [44], we introduced two minor changes in Eqns (E1). First, a factor $Z(1/3)$ (included in B^{Voigt}) was added to better evaluate the average contact stiffnesses. Then we specified that the backbone coordination number, z^* , corrected for the proportion of rattlers, should be used, rather than the global mechanical coordination number, z , because the elastic moduli simply coincide with those of the packing stripped of its rattlers. This precision is necessary because, unlike in the example calculations of [44], we deal with configurations, such as C and D, with a non-negligible fraction of rattlers x_0 .

[1] I. Agnolin and J.-N. Roux, *Internal states of model isotropic granular packings: Assembling process, geom-*

etry and contact networks, first companion paper (2007).
[2] I. Agnolin and J.-N. Roux, *Internal states of model*

- isotropic granular packings: compression and pressure cycles*, second companion paper (2007).
- [3] D. Cumberland and R. Crawford, *The Packing of Particles* (Elsevier, Amsterdam, 1987).
- [4] D. Bideau and J. Dodds, eds., *Physics of Granular Media* (Nova Science Publishers, 1991).
- [5] J. Duffy and R. Mindlin, *Journal of Applied Mechanics ASME* **24**, 585 (1957).
- [6] R. Kuwano and R. J. Jardine, *Géotechnique* **52**, 727 (2002).
- [7] B. Gilles and C. Coste, *Physical Review Letters* **90**, 174302 (2003).
- [8] H. A. Makse, N. Gland, D. L. Johnson, and L. Schwartz, *Physical Review E* **70**, 061302 (2004).
- [9] S. N. Domenico, *Geophysics* **42**, 1339 (1977).
- [10] C. Thornton, *Géotechnique* **50**, 43 (2000).
- [11] A. S. J. Suiker and N. A. Fleck, *ASME Journal of Applied Mechanics* **71**, 350 (2004).
- [12] H. Makse, N. Gland, D. Johnson, and L. Schwartz, *Physical Review Letters* **83**, 5070 (1999).
- [13] L. E. Silbert, D. Ertas, G. S. Grest, T. C. Halsey, and D. Levine, *Physical Review E* **65**, 031304 (2002).
- [14] L. E. Silbert, G. S. Grest, and J. W. Landry, *Physical Review E* **66**, 061303 (2002).
- [15] S. Shibuya, F. Tatsuoka, S. Teachavorasinskun, X.-J. Kong, F. Abe, Y.-S. Kim, and C.-S. Park, *Soils and Foundations* **32**, 26 (1992).
- [16] P.-Y. Hicher, *ASCE Journal of Geotechnical Engineering* **122**, 641 (1996).
- [17] H. Geoffroy, H. di Benedetto, A. Duttine, and C. Sauzéat, in *Deformation characteristics of geomaterials*, edited by H. di Benedetto, T. Doanh, H. Geoffroy, and C. Sauzéat (Swets and Zeitlinger, Lisse, 2003), pp. 353–363.
- [18] Y.-C. Chen, I. Ishibashi, and J. T. Jenkins, *Géotechnique* **38**, 23 (1988).
- [19] Y.-C. Chen, I. Ishibashi, and J. T. Jenkins, *Géotechnique* **38**, 33 (1988).
- [20] T. G. Thomann and R. D. Hryciw, *ASTM Geotechnical Testing Journal* **13**, 97 (1990).
- [21] X. Jia, C. Caroli, and B. Velický, *Phys. Rev. Lett.* **82**, 1863 (1999).
- [22] X. Jia and P. Mills, in *Powders and Grains 2001*, edited by Y. Kishino (Swets & Zeitlinger, Lisse, 2001), pp. 105–112.
- [23] M. Sharifipour, C. Dano, and P.-Y. Hicher, *Wave velocities in assemblies of glass beads using bender-extender elements*, Proceedings of the "Engineering Mechanics 2004" symposium of the American Society of Civil Engineering, on CD-ROM (2004).
- [24] I. Agnolin, J.-N. Roux, P. Maassad, X. Jia, and P. Mills, in [74], pp. 313–317.
- [25] F. Tatsuoka, in *Geotechnics for roads, rail tracks and earth structures*, edited by G. Correia and H. Brandle (Balkema, Lisse, 2001), pp. 69–140.
- [26] H. di Benedetto, T. Doanh, H. Geoffroy, and C. Sauzéat, eds., *Deformation characteristics of geomaterials: Recent investigations and prospects* (Swets and Zeitlinger, Lisse, 2003).
- [27] P. A. Vermeer, in *Physics of Dry Granular Media*, edited by H. J. Herrmann, J.-P. Hovi, and S. Luding (Balkema, Dordrecht, 1998), pp. 163–196.
- [28] K. Walton, *Journal of Mechanics and Physics of Solids* **35**, 213 (1987).
- [29] J. T. Jenkins, D. Johnson, L. La Ragione, and H. Makse, *Journal of The Mechanics and Physics of Solids* **53**, 197 (2005).
- [30] E. Somfai, J.-N. Roux, J. Snoeijer, M. van Hecke, and W. van Saarloos, *PRE* **72**, 021301 (2005).
- [31] J.-N. Roux, in *Proceedings of the Saint-Venant Symposium on Multiple Scale Analysis and Coupled Physical Systems* (Presses de l'Ecole Nationale des Ponts et Chaussées, Paris, 1997), pp. 577–584.
- [32] J.-N. Roux, *Physical Review E* **61**, 6802 (2000).
- [33] M. Parrinello and A. Rahman, *Journal of Applied Physics* **52**, 7182 (1981).
- [34] M. Parrinello and A. Rahman, *Journal of Chemical Physics* **76**, 2662 (1982).
- [35] K. L. Johnson, *Contact Mechanics* (Cambridge University Press, 1985).
- [36] N. P. Kruyt and L. Rothenburg, *International Journal of Solids and Structures* **39**, 311 (2002).
- [37] S. Nemat-Nasser and M. Hori, *Micromechanics*. (North-Holland, 1993).
- [38] H. P. Zhang and H. A. Makse, *Physical Review E* **72**, 011301 (2005).
- [39] J. D. Goddard, *Proc. Roy. Soc. London* **430**, 105 (1990).
- [40] P.-G. de Gennes, *Europhysics Letters* **35**, 145 (1996).
- [41] J.-N. Roux, in *Powders and Grains 97*, edited by R. P. Behringer and J. Jenkins (Balkema, Rotterdam, 1997), pp. 215–218.
- [42] B. Velický and C. Caroli, *Physical Review E* **65**, 021307 (2002).
- [43] N. P. Kruyt and L. Rothenburg, *Mechanics of Materials* **36**, 1157 (2004).
- [44] L. La Ragione and J. T. Jenkins, *Proceedings of the Royal Society A* **463**, 735 (2007).
- [45] I. Agnolin and J.-N. Roux, submitted to *International Journal of Solids and Structures* (2006).
- [46] C. O'Hern, L. E. Silbert, A. J. Liu, and S. R. Nagel, *Physical Review E* **68**, 011306 (2003).
- [47] M. Wyart, Ph.D. thesis, École Polytechnique (2005), cond-mat/05-12155.
- [48] M. Wyart, *Annales de Physique Fr.* **30**, 1 (2006).
- [49] M. Wyart, S. R. Nagel, and T. A. Witten, *Europhysics Letters* **72**, 486 (2005).
- [50] D. M. Wood, *Soil Behaviour and Critical State Soil Mechanics* (Cambridge University Press, 1990).
- [51] J. K. Mitchell, *Fundamentals of soil behavior* (Wiley, New York, 1993).
- [52] J. Biarez and P.-Y. Hicher, *Elementary Mechanics of Soil Behaviour* (A. A. Balkema, Rotterdam, 1993).
- [53] G. Combe and J.-N. Roux, *Physical Review Letters* **85**, 3628 (2000).
- [54] J.-N. Roux, in [74], pp. 261–265.
- [55] J.-N. Roux and G. Combe, *C. R. Académie des Sciences (Physique)* **3**, 131 (2002).
- [56] L. Staron, J.-P. Vilotte, and F. Radjai, *Physical Review Letters* **89**, 204302 (2002).
- [57] G. Combe, *Mécanique des matériaux granulaires et origines microscopiques de la déformation* (Presses du Laboratoire Central des Ponts et Chaussées, Paris, 2002).
- [58] M. E. Cates, W. J. P., J.-P. Bouchaud, and P. Claudin, *Philosophical Transactions of the Royal Society of London* **356**, 2535 (1998).
- [59] G. Combe and J.-N. Roux, in preparation.
- [60] A. Tanguy, J. P. Wittmer, F. Leonforte, and J.-L. Barrat, *Physical Review B* **66** (2002).

- [61] F. Leonforte, R. Boissière, A. Tanguy, J. P. Wittmer, and J.-L. Barrat, *Physical Review B* **72** (2005).
- [62] C. Maloney and A. Lemaître, *Physical Review E* **74**, 0116118 (2006).
- [63] M. R. Kuhn and C. S. Chang, *International Journal of Solids and Structures* **43**, 6026 (2006).
- [64] K. Bagi, *Granular Matter* **9**, 109 (2007).
- [65] S. McNamara and H. J. Herrmann, *Physical Review E* **74**, 021304 (2006).
- [66] F. Radjai and S. Roux, *Physical Review Letters* **89**, 064302 (2002).
- [67] A. Donev, R. Connelly, F. H. Stillinger, and S. Torquato, *Hypostatic Jammed Packings of Nonspherical Hard Particles: Ellipses and Ellipsoids*, preprint (archive cond-mat 0608334) (2006).
- [68] T. Matsushima, in [74], pp. 1319–1323.
- [69] D. Elata and J. G. Berryman, *Mechanics of Materials* **24**, 229 (1996).
- [70] R. D. Mindlin and H. Deresiewicz, *ASME Journal of Applied Mechanics* **20**, 327 (1953).
- [71] C. Thornton and C. W. Randall (Elsevier, Amsterdam, 1988), pp. 245–252.
- [72] J. T. Jenkins and L. La Ragione, *International Journal of Solids and Structures* **38**, 1063 (2001).
- [73] C. Gay and R. A. da Silveira, *Europhysics Letters* **68**, 51 (2004).
- [74] R. García Rojo, H. J. Herrmann, and S. McNamara, eds., *Powders and Grains 2005* (Balkema, Leiden, 2005).