



HAL
open science

Crystal structure and magnetic properties of [Co(H₂O)₂Mo(CN)₈]₄ H₂O, a three-dimensional cyanide-bridged bimetallic compound

Floriana Tuna, Stéphane Golhen, Lahcène Ouahab, Jean-Pascal Sutter

► **To cite this version:**

Floriana Tuna, Stéphane Golhen, Lahcène Ouahab, Jean-Pascal Sutter. Crystal structure and magnetic properties of [Co(H₂O)₂Mo(CN)₈]₄ H₂O, a three-dimensional cyanide-bridged bimetallic compound. *Comptes Rendus. Chimie*, 2003, 6 (3), pp.377-383. 10.1016/S1631-0748(03)00053-5. hal-00184548

HAL Id: hal-00184548

<https://hal.science/hal-00184548>

Submitted on 4 Mar 2024

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Full paper / Mémoire

Crystal structure and magnetic properties of $[\{Co(H_2O)_2\}_2Mo(CN)_8] \cdot 4 H_2O$, a three-dimensional cyanide-bridged bimetallic compound

Floriana Tuna^{a,c}, Stéphane Golhen^{b,1}, Lahcène Ouahab^b, Jean-Pascal Sutter^{a,*}^a Institut de chimie de la matière condensée de Bordeaux, UPR CNRS 9048, 33608 Pessac, France^b Laboratoire de chimie du solide et inorganique moléculaire, UMR CNRS 6511, université Rennes-1, 35042 Rennes, France^c Institute of Physical Chemistry of the Romanian Academy, 77208 Bucharest, Romania

Received 4 November 2002; accepted 19 February 2003

Abstract

The three-dimensional cyano-bridged bimetallic compound of formula $[\{Co(H_2O)_2\}_2Mo(CN)_8] \cdot 4 H_2O$ is described. The single-crystal X-ray structural determination revealed that the compound has a polymeric structure based on a network of $[Mo^{IV}(CN)_8]$ units and Co^{II} ions. Each $Mo(CN)_8$ building block is linked to Co ions through its eight CN ligands and each Co^{II} centre is connected to four Mo units forming a highly symmetrical three-dimensional framework with square-shaped channels running through the structure. The magnetic behaviour in the temperature range 2–300 K and spectroscopic data are reported as well. *To cite this article: F. Tuna et al., C. R. Chimie 6 (2003).*

© 2003 Académie des sciences. Published by Éditions scientifiques et médicales Elsevier SAS. All rights reserved.

Résumé

Le composé hétérobimétallique à ponts cyanure de formulation $[\{Co(H_2O)_2\}_2Mo(CN)_8] \cdot 4 H_2O$ et caractérisé par une architecture tri-dimensionnelle est décrit. La détermination de sa structure cristalline par diffraction des rayons X sur monocristal a mis en évidence sa nature polymère, basée sur un réseau d'unités $[Mo^{IV}(CN)_8]$ et d'ions Co^{II} . Chaque élément $[Mo(CN)_8]$ est lié à des ions Co par chacun de ses huit ligands CN, tandis que chaque Co est connecté à quatre unités Mo pour engendrer un édifice tridimensionnel. La structure ainsi formée est poreuse et parcourue par des canaux de section carrée. Les propriétés magnétiques de ce composé dans le domaine de température 2–300 K ainsi que ses caractéristiques spectroscopiques sont également décrites. *Pour citer cet article : F. Tuna et al., C. R. Chimie 6 (2003).*

© 2003 Académie des sciences. Published by Éditions scientifiques et médicales Elsevier SAS. All rights reserved.

Keywords: cyanometalate; molybdenum complex; cobalt complex; magnetic properties; crystal structure; supramolecular material; porous framework

Mots clés : cyanométallate ; molybdène ; cobalt ; propriété magnétique ; matériau supramoléculaire ; matériau poreux ; structure cristallographique

* Corresponding author.

E-mail address: jpsutter@icmcb.u-bordeaux.fr (J.-P. Sutter).¹ Author to whom inquiries related to the crystallographic studies could be addressed. Fax: (int-33)–540 00 26 49.

1. Introduction

Cyanide-bridged bimetallic assemblies based on cyanometalate building blocks, $[\text{M}(\text{CN})_m]^{q-}$, have attracted considerable recent interest in the area of molecule-based magnets [1, 2]. One of the advantages of using cyanide ligands when building magnetic materials is that they can mediate strong exchange interactions between the interconnected paramagnetic metal centres. A prominent example is the Prussian Blue family, based on the hexacyanometallates [3–9]. This family of 3d ion compounds has provided examples of magnets with critical temperatures as high as 376 K, and materials with interesting electrochemical, optoelectronic and magneto-optical properties.

Paramagnetic 4d and 5d metal ions have been envisaged only recently for the construction of molecule-based magnets [10]. Owing to the more spatially extended d orbitals for these elements, stronger exchange interactions are anticipated between magnetic centres and, consequently, magnetic ordering at higher temperatures. A synthetic approach that we currently investigate in our laboratories is based on the use of the low-symmetrical $[\text{Mo}^{\text{III}}(\text{CN})_7]^{4-}$ as a building block; several two- and three-dimensional 3d–4d bimetallic compounds have been obtained [11, 12]. For instance, reaction of $[\text{Mo}(\text{CN})_7]^{4-}$ with Mn^{2+} ions permitted to obtain three cyanide-bridged bimetallic compounds exhibiting long-range magnetic ordering at T_c as high as 51 K, along with a pronounced magnetic anisotropy [13]. A higher ordering temperature is obtained when asymmetry is imposed not only to the Mo^{III} sites but also to the Mn^{II} centre. Using triethanolamine (*tea*) as an additional ligand, we recently prepared the 3D bimetallic assembly $[\text{Mn}_2(\text{tea})\text{Mo}(\text{CN})_7]$, which exhibits long-range magnetic ordering below $T_c = 106$ K [14].

We further reasoned that, using Co^{2+} instead of Mn^{2+} , it should be possible to enforce a higher magnetic coercivity for the material. Surprisingly, the reaction of $[\text{Mo}(\text{CN})_7]^{4-}$ with CoX_2 ($X = \text{nitrate}$ or perchlorate), under strictly anaerobic conditions, did not afford the expected compound, but crystals of the 3D bimetallic assembly $[\{\text{Co}(\text{H}_2\text{O})_2\}_2\text{Mo}(\text{CN})_8] \cdot 4 \text{H}_2\text{O}$, whose structure and magnetic properties are reported here.

2. Results and discussion

2.1. Preparation and structural features

The reaction of $\text{K}_4[\text{Mo}(\text{CN})_7] \cdot 2 \text{H}_2\text{O}$ with $[\text{Co}(\text{H}_2\text{O})_6]\text{X}_2$ ($X^- = \text{NO}_3^-$ or ClO_4^-) in a slow diffusion process of aqueous solutions affords the 3-D cyanide-bridged bimetallic compound of formula $[\text{Co}_2(\text{H}_2\text{O})_4\text{Mo}(\text{CN})_8] \cdot 4 \text{H}_2\text{O}$, **1**. Orange octahedral crystals of **1** are formed reproducibly in an H-shaped tube from deoxygenated solutions of reagents. A rational preparation for compound **1** starting from $[\text{Mo}^{\text{IV}}(\text{CN})_8]^{4-}$ and $[\text{Co}(\text{H}_2\text{O})_6]^{2+}$ was reported by McKnight et al. [15]. However, following the described synthetic procedure, a powdered sample is formed and the crystal structure of the compound remained unknown.

The single-crystal X-ray structural determination revealed that **1** has a polymeric structure based on a network of $[\text{Mo}(\text{CN})_8]$ units and $[\text{Co}^{\text{II}}(\text{H}_2\text{O})_2]$ ions. The axial-coordinated water molecules point directly into the channels of the network and are involved in H-bonding interactions with H_2O solvated molecules located in the void of the framework (Fig. 1). The geometry of the $\text{Mo}(\text{CN})_8$ unit is close to a square

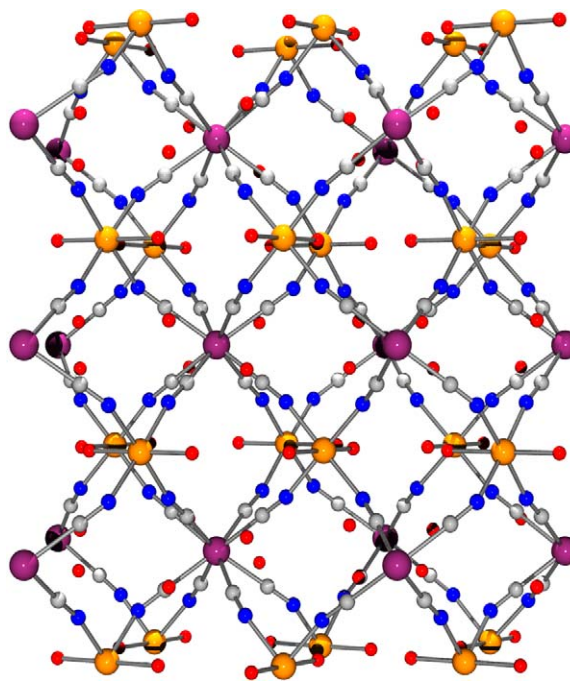


Fig. 1. View of the 3D arrangement of $[\{\text{Co}(\text{H}_2\text{O})_2\}_2\text{Mo}(\text{CN})_8] \cdot 4 \text{H}_2\text{O}$ down the b direction.

2.2. Spectroscopic characteristics

The IR spectrum of the crystalline compound shows only one ν_{CN} band centred at 2138 cm^{-1} , supporting the formation of $\text{Mo}^{\text{IV}}\text{-CN-Co}^{\text{II}}$ linkages [15, 17]. Two broad bands centred at 3554 and 3406 cm^{-1} are due to O–H stretching modes and support the presence of both coordinated and non-coordinated water molecules in **1**. The diffuse reflectance electronic spectrum shows the superposition of characteristic bands of the $[\text{Mo}^{\text{IV}}(\text{CN})_8]^{4-}$ (380 and 430 nm) and Co^{II} (490 nm) fragments [20]. No additional absorption that could be attributed to metal-to-metal charge-transfer bands was observed.

2.3. Magnetic properties

The temperature dependence of the molar magnetic susceptibility, χ_{M} , of compound **1** was measured on a polycrystalline sample in the temperature range 5–300 K using a SQUID magnetometer. The result, plotted as $\chi_{\text{M}}T$ versus T in Fig. 4, shows that the value for $\chi_{\text{M}}T$ decreases from $5.9\text{ cm}^3\text{ K mol}^{-1}$ at 300 K to $3.65\text{ cm}^3\text{ K mol}^{-1}$ at 5 K. The decrease of $\chi_{\text{M}}T$ with T can be attributed to the intrinsic behaviour of Co^{II}

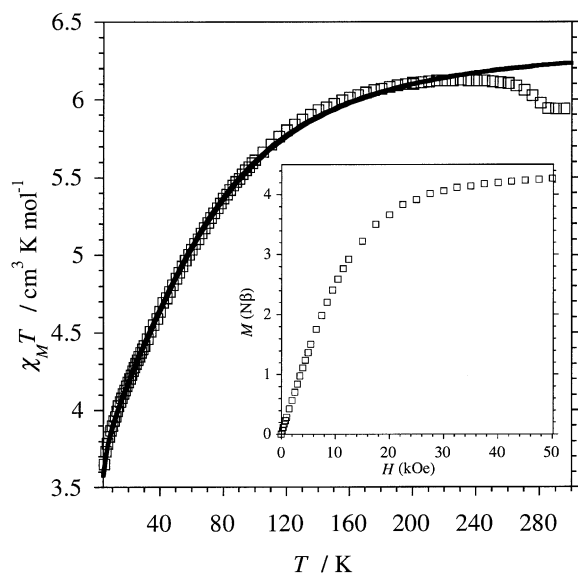


Fig. 4. Temperature dependence for the experimental (\square) and calculated (—) $\chi_{\text{M}}T$ for $[\text{Co}(\text{H}_2\text{O})_2]_2\text{Mo}(\text{CN})_8 \cdot 4\text{H}_2\text{O}$ yielding $g = 2.604 \pm 0.001$, $D = -80.3 \pm 0.6\text{ cm}^{-1}$ and $\theta = -0.36 \pm 0.01\text{ K}$. Insert: Field dependence of the magnetization recorded at 2 K.

rather than to antiferromagnetic exchange interactions among these ions in the 3D network. This is confirmed by the field dependence of the magnetization recorded at 2 K, which reaches a saturation value of $4.25\ \mu_{\text{B}}$ for 5 T (Fig. 4, insert).

The high-temperature $\chi_{\text{M}}T$ value obtained for compound **1** is much larger than the spin-only value expected for two $S = 3/2$ spins ($3.75\text{ cm}^3\text{ K mol}^{-1}$). This deviation is the result of the first-order orbital momentum displayed by high-spin Co^{II} ions in octahedral surrounding. Moreover, in addition to the symmetry lowering due to the deformation of the octahedral coordination sphere of the Co ions, the coupling of the first-order orbital momentum with the spin momentum partially removes the degeneracy of the ground state and the excited states. This results in an energy spectrum for a high-spin Co^{II} ion where the two low-lying levels correspond to the $M_S = \pm 1/2$ and $\pm 3/2$ states. Taking into account the Zeeman perturbation resulting from the applied external field, the Hamiltonian describing this situation is [21]:

$$\mathbf{H} = \Delta (\mathbf{L}_z^2 - 2/3) - (3/2) \kappa \lambda \mathbf{L} \cdot \mathbf{S} + \beta [-(3/2) \kappa \mathbf{L} + g_e \mathbf{S}] \cdot \mathbf{H}$$

This expression includes the energy gap between the states split by the deformation of the coordination sphere, Δ , a spin-orbit coupling parameter, λ , and a parameter κ , called the orbital reduction factor accounting for the effect of the M–ligand bond on the orbital momentum. A model taking into account all these parameters to fit the experimental magnetic data would be over-parameterised. Therefore, it is usual to consider that Δ is large enough to have only the two lowest Kramer doublets thermally populated in the investigated temperature range. The energy separation D between these levels is then considered as a zero-field splitting within the quartet state. The Hamiltonian considered in that case becomes $\mathbf{H} = D [\mathbf{S}_z^2 - S(S+1)/3] + \beta \mathbf{g} \cdot \mathbf{S} \cdot \mathbf{H}$. The orbital momentum does not longer appear but its influence is incorporated into both D and \mathbf{g} parameters.

The theoretical expression for the molar susceptibility deduced for this spin Hamiltonian is given in eq. (1) [22]. It considers the paramagnetic behaviour for the two independent Co^{II} ions found in the molecular formula. Possible weak interactions between the $\text{Co}(\text{II})$

sites within the network are considered through a Curie–Weiss parameter θ .

$$\chi_M = 2 \left[\frac{N \mu_B^2 g_{Co}^2}{3 k (T - \theta)} \frac{1 + 9 e^{-2D/kT}}{4 (1 + e^{-2D/kT})} + \frac{2N \mu_B^2 g_{Co}^2}{3 k (T - \theta)} - \frac{4 + \frac{3kT}{D} (1 - e^{-2D/kT})}{4 (1 + e^{-2D/kT})} \right] \quad (1)$$

Best fit to the experimental data in the temperature domain 5–250 K leads to $g_{Co} = 2.604 \pm 0.001$, $D = -80.3 \pm 0.6 \text{ cm}^{-1}$ and $\theta = -0.36 \pm 0.01 \text{ K}$ (Fig. 4). The small θ value is consistent with weak antiferromagnetic interactions between the Co(II) ions through the diamagnetic NC–Mo^{IV}–CN bridges. Such a weak exchange through this spacer has been observed previously in related compounds with Mn^{II} and Cu^{II} instead of Co^{II} ions [18]. The data above 250 K have not been considered for the parameterisation, because of the small step visible close to 270 K. This discontinuity in the magnetic behaviour is attributed to a slight distortion of framework occurring for these temperatures.

An analysis of the field dependence of the magnetization with the Brillouin function by considering $g_{Co} = 2.60$ indicates that at 2 K the effective spin for the Co^{II} ions in compound **1** is still above $S = 1/2$.

Both the spectroscopic data and the magnetic study are consistent with a Mo ion in oxidation state IV. Thus, in the course of the crystallization process, the 4d metal ion is oxidized from Mo^{III} in [Mo(CN)₇]⁴⁻ to Mo^{IV} in the diamagnetic [Mo(CN)₈] building block of the framework. The mechanism for this oxidation process remains unclear, but the propensity for [Mo(CN)₇]⁴⁻ to easily be oxidized to [Mo(CN)₈]⁴⁻ has been reported before [23]. An analogous oxidation process was observed in a related self-assembling procedure involving [Mo(CN)₇] and an Mn^{II} compound [24]. In both cases, the reactions were performed under strictly anaerobic conditions and no other compound could be detected in the solid state.

3. Concluding remark

The evolution of [Mo(CN)₇]⁴⁻ during the slow crystallization process in the presence of Co^{II} ions leads to the formation of single crystal of [{Co(H₂O)₂]₂Mo(CN)₈}]·4 H₂O. This provided the opportunity to investigate the crystal structure for this

compound, revealing its 3D nature. Interestingly, this compound exhibits a porous framework with square-shaped channel running through the structure. Its magnetic properties are mainly governed by the zero-field splitting due to the Co ions.

4. Experimental

The commercial chemicals were used as received without further purification. K₄[Mo(CN)₇]·2 H₂O was synthesized as described in the literature [18]. All physical measurements were performed on macroscopic crystals ground to a powder. Infrared spectra (400–4000 cm⁻¹) were recorded from KBr pellets on a Perkin-Elmer Paragon 1000 FTIR spectrometer. UV–Vis spectra (diffuse reflectance technique) were recorded with a UV–4 (Unicam) spectrophotometer. Variable-temperature (2–300 K) magnetic susceptibility measurements were carried out with a Quantum Design MPMS–5S SQUID magnetometer under an applied magnetic field of 5000 G. Diamagnetic corrections were estimated from Pascal tables and magnetic data were corrected for diamagnetic contributions of the sample holder.

4.1. Synthesis

Orange octahedral crystals of [{Co(H₂O)₂]₂Mo(CN)₈}]·4 H₂O were obtained by slow diffusion, in an H-shaped tube ($V = 60 \text{ ml}$) under nitrogen, of two deoxygenated 5-ml aqueous solutions containing 35 mg (0.075 mmol) of K₄[Mo(CN)₇]·2 H₂O and 43 mg (1.5 mmol) of Co(NO₃)₂·6 H₂O, respectively. The crystals were carefully collected, washed with water and ethanol, and finally dried under a flow of N₂. Yield: 30–35%.

A second sample generated by slow interdiffusion of two aqueous solutions of K₄[Mo(CN)₇]·4 H₂O (55 mg) and Co(ClO₄)₂·6H₂O (60 mg) in an H-tube, proved to correspond to the same compound.

Elem. anal.: calcd for C₈H₁₆N₈O₈Co₂Mo: C, 16.97, H, 2.85; Co, 20.82; Mo, 16.95; N, 19.79%; found: C, 17.00; H, 2.81; Co, 20.83; Mo, 16.88; N, 19.68%. Selected IR data (KBr, cm⁻¹): 3554, 3406, 2138, 451, 420.

4.2. Solution and refinement of the X-ray structure

Crystal data and structure refinement of [{Co(H₂O)₂]₂Mo(CN)₈}]·4 H₂O, **1** are given in Table 1.

Table 1
Crystal data and structure refinement of $[\{\text{Co}(\text{H}_2\text{O})_2\}_2\text{Mo}(\text{CN})_8]\cdot 4\text{H}_2\text{O}$, **1**.

Empirical formula	$\text{C}_8\text{H}_{16}\text{Co}_2\text{MoN}_8\text{O}_8$
Formula weight	566.09
Temperature (K)	293(2)
Crystal system	Tetragonal
Space group	$I4/m$
a (Å)	11.7306(4)
c (Å)	13.0372(5)
V (Å ³)	1794.02(11)
Z	4
D_c (g cm ⁻³)	2.096
m (mm ⁻¹)	2.573
Reflections collected	4034
Independent reflections	2479
Parameters	67
Goodness-of-fit on F^2	1.039
Final R indices	$R_1 = 0.0434$
$[I > 2\sigma(I)]$	$wR_2 = 0.0860$
R indices (all data)	$R_1 = 0.0699$
	$wR_2 = 0.0964$

A single crystal of the title compound was mounted on glass fibre and transferred to a Kappa Nonius four circle diffractometer equipped with a CCD camera and a graphite monochromated Mo $K\alpha$ radiation source ($\lambda = 0.71073$ Å). Data were collected at room temperature, then, treated using DENZO and SCALEPACK [25], no absorption correction were performed. Crystal of $[\text{Co}(\text{H}_2\text{O})_2]_2[\text{Mo}(\text{CN})_8]\cdot 4\text{H}_2\text{O}$ crystallizes in the tetragonal space group $I4/m$, $a = b = 11.7306(4)$ Å, $c = 13.0372(5)$ Å, $V = 1794.0(1)$ Å³, $Z = 4$. Data were refined with SHELXL-97 [26] program by full matrix least squares method, on F^2 ; refinement of variables were performed with anisotropic thermal parameters for all non-hydrogen atoms. 4034 reflections (completeness to $37.74^\circ = 99.6\%$) were collected giving rise to $R_{\text{int}} = 0.0411$. Refinements of 67 parameters gave $R_1 = 0.0434$ and $wR_2 = 0.860$ for 1847 data $\geq 2\sigma(I)$ and $R_1 = 0.0699$, $wR_2 = 0.0964$ for 2479 unique data. No H atoms from water molecules were included in this model, the residual electron-density being in the range -1.316 to $+1.580$ e Å⁻³ with the largest peak trough close to the oxygen atoms from iron-coordinated water molecules. Despite to these peaks, and contrary to a related structure [19], no disorder between coordinated water molecules is observed.

5. Supplementary material

The supplementary material has been sent to the Cambridge Crystallographic Data Centre, 12 Union Road, Cambridge, CB2 1EZ, UK as supplementary material No. 195769 (CIF) and can be obtained by contacting the CCDC (fax: +44-1223-336033; e-mail: deposit@ccdc.cam.ac.uk or www: <http://www.ccdc.cam.ac.uk>).

Acknowledgements

This work was supported by the French Ministry of Research (fellowship to FT) and the TMR Research Network of the European Union entitled ‘Molecular Magnetism: from Materials toward Devices’.

References

- [1] M. Verdager, A. Bleuzen, V. Marvaud, J. Vaissermann, M. Seuleiman, C. Desplanches, A. Sculler, C. Train, R. Garde, G. Gelly, C. Lomenech, I. Rosenman, P. Veillet, C. Cartier, F. Villain, *Coord. Chem. Reviews* 190–192 (1999) 1023.
- [2] M. Ohba, K. Okawa, *Coord. Chem. Rev.* 189 (2000) 313.
- [3] D. Babel, *Comments Inorg. Chem.* 5 (1982) 285.
- [4] S. Ferlay, T. Mallah, R. Ouahes, P. Veillet, M. Verdager, *Nature* 378 (1995) 701.
- [5] W. Entley, G.S. Girolami, *Science* 268 (1995) 397.
- [6] O. Sato, T.I. Yoda, A. Fujishina, K. Hashimoto, *Science* 272 (1996) 704.
- [7] S.M. Holmes, G.S. Girolami, *J. Am. Chem. Soc.* 121 (1999) 5593.
- [8] O. Hatlevik, W.E. Buschmann, J. Zhang, J.L. Manson, J.S. Miller, *Adv. Mater.* 11 (1999) 914.
- [9] R. Garde, F. Villain, M. Verdager, *J. Am. Chem. Soc.* 124 (2002) 10531.
- [10] C. Mathonière, J.-P. Sutter, J.V. Yakhmi, in *magnetism: molecules to material* (J.S. Miller, M. Drillon Eds.) Vol. 4, Wiley-VCH, Weinheim, Germany, 2002, 1–40.
- [11] J. Larionova, R. Clérac, J. Sanchiz, O. Kahn, S. Golhen, L. Ouahab, *J. Am. Chem. Soc.* 120 (1998) 13088.
- [12] J. Larionova, O. Kahn, S. Golhen, L. Ouahab, R. Clérac, *J. Am. Chem. Soc.* 121 (1999) 3349.
- [13] O. Kahn, J. Larionova, L. Ouahab, *Chem. Commun.* (1999) 945.
- [14] S. Tanase, F. Tuna, P. Guionneau, T. Maris, G. Rombaut, C. Mathonière, M. Andruh, O. Kahn, J.-P. Sutter, *Inorg. Chem.* 42 (2003) 1625.
- [15] G.F. McKnight, G.R.J. Haight, *Inorg. Chem.* 12 (1973) 3007.
- [16] M. Pilkington, S. Decurtins, *Chimia* 54 (2000) 593.

- [17] A.K. Sra, G. Rombaut, F. Lahitête, S. Golhen, L. Ouahab, C. Mathonière, J.V. Yakhmi, O. Kahn, *New J. Chem.* 24 (2000) 871.
- [18] G. Rombaut, M. Verelst, S. Golhen, L. Ouahab, C. Mathonière, O. Kahn, *Inorg. Chem.* 40 (2001) 1151.
- [19] G. Rombaut, C. Mathonière, P. Guionneau, S. Golhen, L. Ouahab, M. Verelst, P. Lecante, *Inorg. Chim. Acta* 326 (2001) 27.
- [20] J.R. Perumareddi, A.D. Liehr, A.W. Adamson, *J. Am. Chem. Soc.* 85 (1963) 249.
- [21] O. Kahn, *Molecular Magnetism*, VCH, Weinheim, 1993.
- [22] J.C. Noveron, M.S. Lah, R.E. Del Sesto, A.M. Ariff, J.S. Miller, P. Stang, *J. Am. Chem. Soc.* 124 (2002) 6613.
- [23] G.R. Rossman, F.D. Tsay, H.B. Gray, *Inorg. Chem.* 12 (1973) 824.
- [24] A.K. Sra, M. Andruh, O. Kahn, S. Golhen, L. Ouahab, J.V. Yakhmi, *Angew. Chem. Int. Ed. Engl.* 38 (1999) 2606.
- [25] Z. Otwinowski, W. Minor, *Methods Enzymol.* 276 (1997).
- [26] G.M. Sheldrick, *SHELXS-97 Program for Crystal Structure Solution*, Institut für Anorganische Chemie, University of Göttingen, Germany, 1997.