



HAL
open science

Direct observation of the high magnetic field effect on the Jahn-Teller state in TbVO₄

C. Detlefs, F. Duc, Kazeř Z.A., J. Vanacken, P. Frings, W. Bras, J.E. Lorenzo, Canfield P.C., Rikken G.L.J.A.

► **To cite this version:**

C. Detlefs, F. Duc, Kazeř Z.A., J. Vanacken, P. Frings, et al.. Direct observation of the high magnetic field effect on the Jahn-Teller state in TbVO₄. *Physical Review Letters*, 2008, 100 (5), pp.056405. <10.1103/PhysRevLett.100.056405>. <hal-00354897>

HAL Id: hal-00354897

<https://hal.science/hal-00354897v1>

Submitted on 25 May 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



HAL Authorization

Direct observation of the high magnetic field effect on the Jahn-Teller state in TbVO_4

C. Detlefs,¹ F. Duc,² Z. A. Kazeř,³ J. Vanacken,⁴ P. Frings,² W. Bras,⁵ J. E. Lorenzo,⁶ P. C. Canfield,⁷ and G. L. J. A. Rikken²

¹*European Synchrotron Radiation Facility,
B.P. 220, F-38043 Grenoble Cedex, France*

²*Laboratoire National des Champs Magnétiques Pulsés,
143, avenue de Rangueil, F-31400 Toulouse, France*

³*Moscow State University, Leninskye Gory, Moscow, 119992 Russia*

⁴*Pulsveldengroep, Institute for Nanoscale Physics and Chemistry,
Clestijnenlaan 200D, B-3001 Leuven, Belgium*

⁵*Netherlands Organisation for Scientific Research (NWO),
DUBBLE CRG at the ESRF, BP220, F-38043 Grenoble, France*

⁶*Institut Néel, CNRS, BP 166X, F-38043 Grenoble, France*

⁷*Ames Laboratory, USDOE and Department of Physics and Astronomy,
Iowa State University, Ames, IA 50011, USA*

(Dated: Version February 5, 2020)

Abstract

We report the first direct observation of the influence of high magnetic fields on the Jahn-Teller (JT) transition in TbVO_4 . Contrary to spectroscopic and magnetic methods, X-ray diffraction directly measures the JT distortion; the splitting between the (311)/(131) and (202)/(022) pairs of Bragg reflections is proportional to the order parameter. Our experimental results are compared to mean field calculations, taking into account all possible orientations of the grains relative to the applied field, and qualitative agreement is obtained.

PACS numbers: 75.25.+z, 75.10.-b

Phase transitions induced by quadrupolar interactions have recently received much attention, mostly due to their influence on the magnetic properties of the sample, e.g. in the giant-magneto-resistive effect of manganite compounds [1] and the magneto-electric effect in multi-ferroic materials [2, 3]. The cooperative Jahn-Teller (JT) effect arises from the same quadrupolar interactions [4], and may indeed be interpreted as ferro-quadrupolar order. In JT compounds, the balance between magnetic and quadrupolar effects can be tuned by varying the strength of an externally applied magnetic field. To date, however, only a small amount of experimental evidence has been reported [5], as the required magnetic fields tend to be rather large.

In this letter we present the first direct experimental evidence for the modification of the JT effect by an external magnetic field. This effect was predicted by both qualitative [6, 7] and quantitative [8, 9] theories, but previous experiments [5, 9, 10, 11, 12] observed only indirect signatures of this behavior.

Terbium ortho-vanadate, TbVO_4 , along with DyVO_4 , is a textbook example for a JT transition [4] induced by quadrupolar interactions between the Tb $4f$ moments, mediated through phonons. At high temperatures, TbVO_4 crystallizes in the tetragonal zircon structure with space group $I4_1/amd$ [13], with lattice parameters $a_t = b_t = 7.1831(3)$ Å and $c = 6.3310(4)$ Å. Upon lowering the temperature through $T_Q \approx 33$ K, it undergoes a cooperative JT transition: The crystal spontaneously distorts along the $[110]$ direction (B_{2g} strain, δ -symmetry distortion) to the orthorhombic space group $Fddd$ with lattice parameters $a_o = 10.239(2)$ Å, $b_o = 10.029(2)$ Å, and $c = 6.3154(13)$ Å at 22 K. The distortion is surprisingly large, reaching $\epsilon^\delta = 2(a_o - b_o)/(a_o + b_o) = 2\%$ at 22 K [13], and increasing further toward lower temperatures.

The JT transition has been studied extensively, both experimentally and theoretically. The early studies, however, focused on the sample's properties in the absence of applied magnetic fields [4]. The effect of large external magnetic fields on TbVO_4 was studied only recently. Quantitative mean-field calculations [8] found that the JT distortion is suppressed when fields above ≈ 29 T are applied along the c -axis of the sample, in good agreement with susceptibility measurements [9]. Diffraction experiments have so far not been carried out, as the required combination of high magnetic fields and X-ray diffraction equipment has only recently become available [14, 15, 16].

The experiments were performed on the DUBBLE CRG beamline, BM26B, at the ESRF

TABLE I: Bragg reflections of TbVO_4 , scattering angle at $E = 21$ keV, and the splitting due to the JT-effect. Values are based in the lattice parameters given in Ref. 13 for $T = 22$ K.

$(HKL)_o$	2θ [deg]	$\delta(2\theta)/\epsilon^\delta$ [deg/%]
(111)	7.14	0
(220)	9.45	0
(311)/(131)	11.78/11.94	0.076
(202)/(022)	12.61/12.69	0.036
(400)/(040)	13.24/13.52	0.134
(222)	14.32	0
(331)	15.19	0
(113)	16.81	0

[17], using the experimental configuration described in [16]. Flux-grown single crystals of TbVO_4 [18, 19] were ground into a fine powder and embedded in low molecular weight polyvinylpyrrolidone in order to prevent movement of the powder grains due to magnetic forces, while at the same time improving the thermal contact. The sample was then mounted in a pulsed magnet and cryostat assembly [16].

The data shown here were taken by accumulating ≈ 45 magnetic field pulses per spectrum. For each field pulse a mechanical shutter exposed the image plate detector for 4.9 ms centered around the maximum field. Representative powder diffraction spectra are shown in Fig. 1.

The JT transition manifests itself as splitting of some, but not all, powder lines (see table I). For small distortions, $\epsilon^\delta \ll 1$, the orthorhombic lattice parameters can be approximated as $a_o \approx (1 + \frac{1}{2}\epsilon^\delta)\bar{a}$ and $b_o \approx (1 - \frac{1}{2}\epsilon^\delta)\bar{a}$, where $\bar{a} = \frac{1}{2}(a_o + b_o) \approx \sqrt{2}a_t$. To first order in ϵ^δ , the splitting of a pair of Bragg reflections $(H, K, L)_o$ and $(K, H, L)_o$ is then given by

$$\delta(2\theta) \approx \frac{\lambda^2 K^2 - H^2}{\bar{a}^2 \sin(2\theta)} \epsilon^\delta = \tan(\theta) \frac{K^2 - H^2}{H^2 + K^2 + \frac{\bar{a}^2}{2c^2} L^2} \epsilon^\delta. \quad (1)$$

Our experimental configuration, with photon energy $E = 21$ keV ($\lambda = 0.59$ Å), allowed us to observe scattering angles up to $2\theta = 12.8^\circ$, covering the reflections, in the orthorhombic notation, (111), (220), (311), (131), (202), and (022). Within this range, only the (311)/(131) and the (202)/(022) pairs are sensitive to the JT distortion.

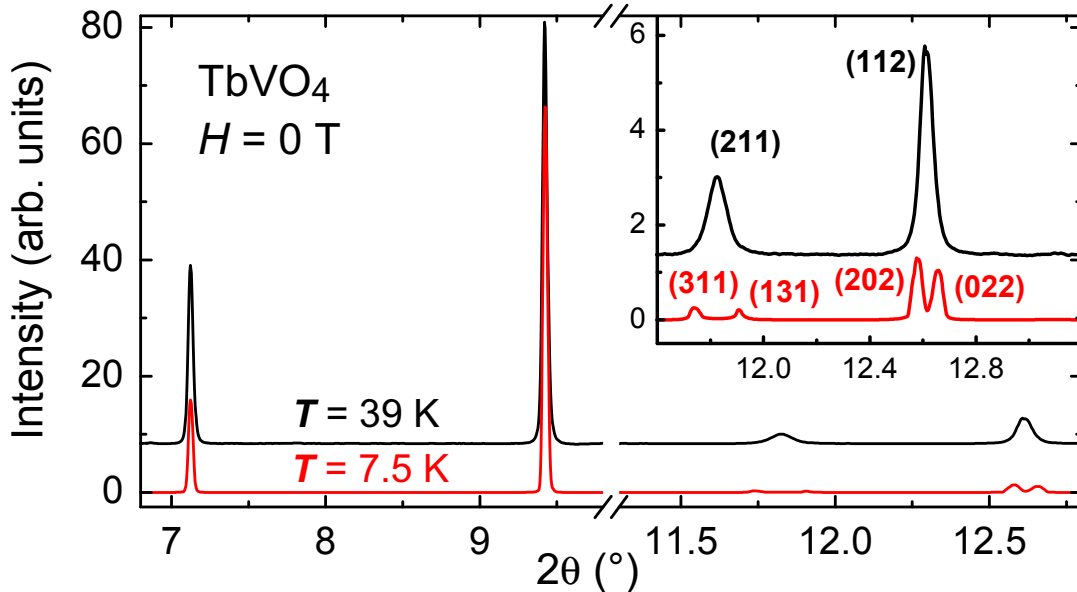


FIG. 1: X-ray powder diffraction spectra of TbVO_4 . The inset shows the $(311)/(131)$ and $(202)/(022)$ pairs of reflections that are sensitive to the orthorhombic distortion, ϵ^δ .

In samples with large magneto-crystalline (MC) anisotropy, such as TbVO_4 , the phase diagram depends not only on the magnitude of an applied magnetic field, but also on its orientation relative to the crystal symmetry axes. The grains in a powder sample are aligned randomly, so that for a macroscopic measurement, e.g. magnetic susceptibility, the direction of the field has to be averaged over the full solid angle of 4π .

In a diffraction experiment, however, the orientation is constrained: Any grain contributing to the diffraction signal at the angle 2θ must be oriented such that the Bragg planes of the corresponding reflection (H, K, L) form the angle θ with the incident beam. The powder averaging must then be taken only over the azimuthal angle, ψ , i.e. rotation about the scattering vector $\mathbf{Q} = (H, K, L)$.

In our experiment the external field, $\mu_0\mathbf{H}$, was aligned along the incident beam axis; the angle between the field and the Bragg planes is therefore the Bragg angle, θ .

For systems with substantial MC anisotropy any simulation of the powder diffraction spectrum must thus be carried out peak by peak: For each Bragg reflection the magnetic field direction and the corresponding influence on the phase diagram and the lattice parameters

must be calculated as function of ψ , yielding, in this case the distortion $\epsilon^\delta(\psi)$, and the corresponding scattering angle, $2\theta_{\text{calc}}(HKL, \epsilon^\delta(\psi))$. The resulting diffraction patterns are then averaged over the azimuthal angle, taking into account the instrumental resolution.

In order to quantitatively describe the effect outlined above for TbVO_4 we have performed comprehensive mean field calculations of the magnetoelastic distortion of TbVO_4 as function of the strength and direction of the externally applied magnetic field. Our calculations closely follow those of [8] and [9] and will be published in full detail elsewhere. In particular, we have used crystal field parameter set 2 of [8], and a quadrupolar constant $G^\delta = 130$ mK.

The order parameter (OP), ϵ^δ , is proportional to the expectation value of the quadrupole operator [23], $Q_{xy} = \langle P_{xy} \rangle$,

$$\epsilon^\delta = \frac{B^\delta}{C_0^\delta} Q_{xy}, \quad (2)$$

where $P_{xy} = \frac{1}{2}(J_x J_y + J_y J_x)$. The coefficient $B^\delta/C_0^\delta = 13.9 \cdot 10^{-4}$ was determined from the zero-field, low temperature value of the spontaneous deformation, ϵ^δ .

We first consider the influence of the applied magnetic field on the quadrupole moment Q_{xy} . Two effects must be taken into account: Changes in the magnitude of the distortion will result in variations of the splitting between the pairs of peaks, whereas (for a given grain) the preferential population of domains with positive or negative distortion will lead to a magnetically induced texture that manifests itself in a shift of spectral weight from one partner to the other.

A magnetic field along the c axis leads to a non-vanishing expectation value of $\langle J_z \rangle$ in competition with the OP. A magnetic field along a_o or b_o , on the other hand, will induce a magnetization $\langle J_x \pm J_y \rangle$ along the corresponding axis. Above the JT transition a magnetostrictive orthorhombic distortion of δ -symmetry is induced. In the ordered state, $T < T_Q$, however, one has to distinguish between a field applied along a_o and b_o : Along the two axes, the susceptibility will be of slightly different value, thus breaking the degeneracy of $\pm\epsilon^\delta$. Crossing the phase boundary in the presence of such a magnetic field will then lead to the preferential population of one of these domains. Fields along the $[110]_o$ directions should lead to a distortion with γ -symmetry (B_{1g} -type), as observed in DyVO_4 [20, 21]. Finally, if the external field is applied along an arbitrary direction, then both δ and γ strains are induced simultaneously, lowering the symmetry of the crystal to monoclinic. Fortunately, the γ magnetostrictive distortion in TbVO_4 is two orders of magnitude smaller than the δ

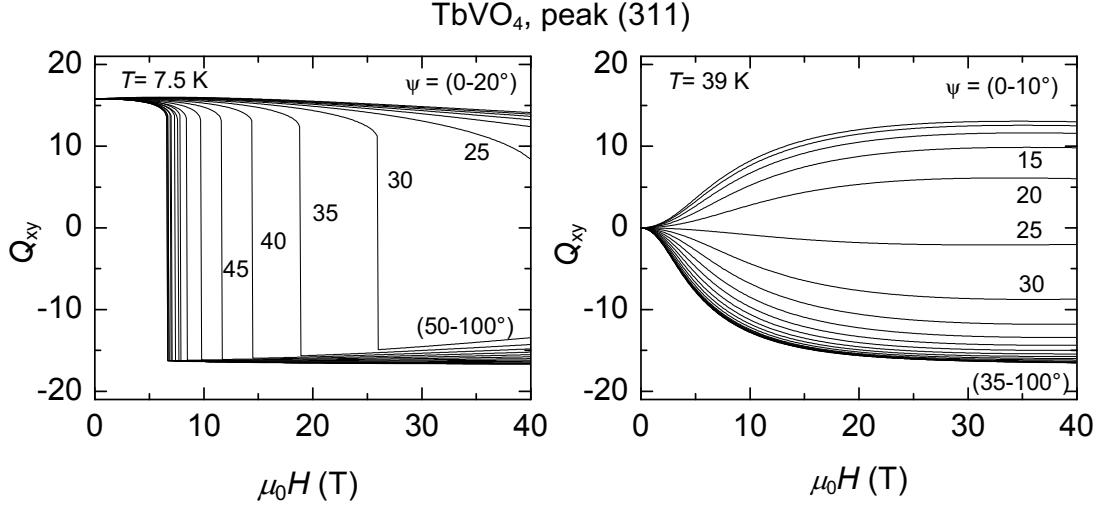


FIG. 2: Calculated dependence of the quadrupole moment Q_{xy} on the external magnetic field for different azimuthal angles in the interval (0–100°) at the diffraction peak (311). Left: $T = 7.5$ K, Right: $T = 39$ K.

distortion and can therefore be neglected.

Typical theoretical results for the (311) diffraction peak at $T = 7.5$ K and 39 K are shown in Fig. 2. The (311) partner of the (311)/(131) pair corresponds to a positive quadrupole moment, $Q_{xy} > 0$ (see eq. 1).

At $T = 39$ K $> T_Q$ there is no spontaneous quadrupole moment at $H = 0$. For azimuthal angles ψ below $\approx 22^\circ$ a positive quadrupole moment is induced, whereas for larger azimuthal angles the induced quadrupole moment is negative, i.e. corresponding to the (131) partner. We thus expect the magnetic field to induce a magnetoelastic splitting with unequal domain populations of $\approx 33\%$ $Q_{xy} > 0$ (contributing to the (311) diffraction peak) and $\approx 67\%$ $Q_{xy} < 0$ (contributing to the (131) diffraction peak) when averaging over the full interval (0–360°).

At $T = 7.5$ K $< T_Q$ the situation is different: A sizable spontaneous quadrupole moment is present, and in a zero-field cooled sample domains with positive and negative Q_{xy} will be populated almost equally. Upon applying an external field the quadrupole moment is reduced, and the degeneracy of $\pm Q_{xy}$ is lifted, so that (depending on their azimuthal angle) domains may invert their quadrupole moment. This transition is first order and therefore

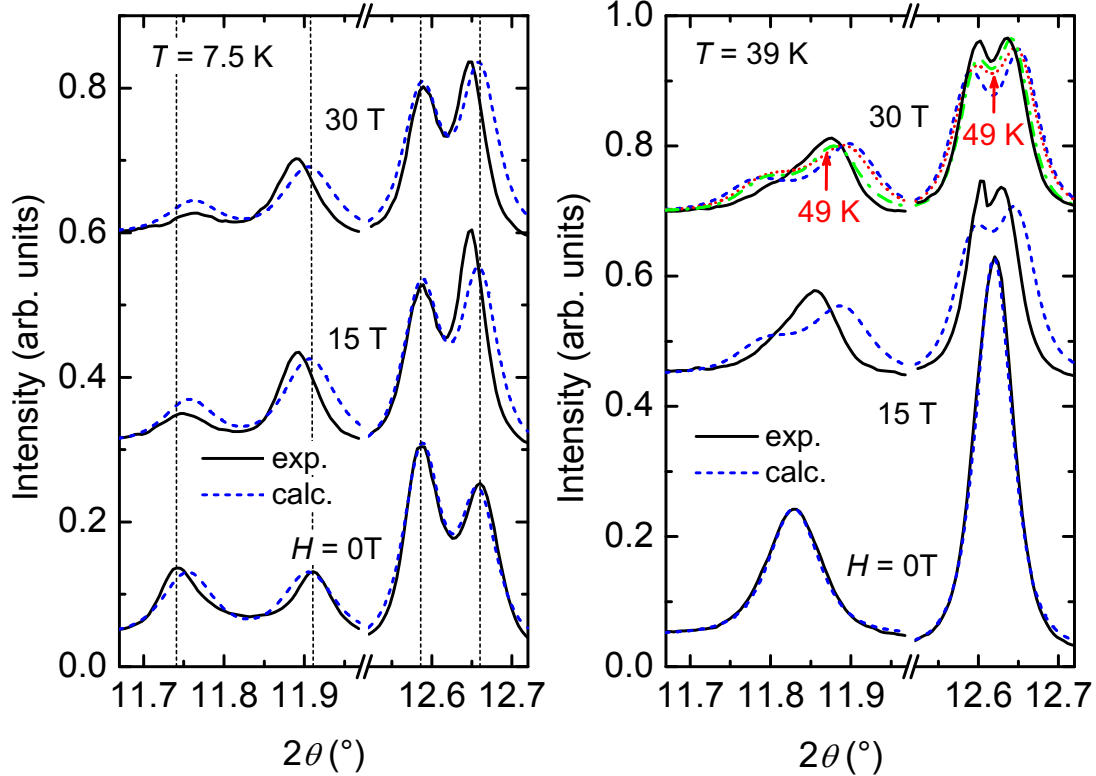


FIG. 3: Comparison between calculated and measured spectra for different temperatures and fields. Left: $T = 7.5$ K. Right: $T = 39$ K. At $T = 39$ K and 30 T, the dotted curve (in red) corresponds to the calculations including the magnetocaloric effect, and the green line to the calculations with the coefficient B^δ/C_0^δ reduced by 25%.

subject to pinning on defects, grain boundaries, surfaces, and elastic interactions between twinned domains [13].

The calculated dependences $Q_{xy}(H)$ for fixed T and different azimuthal angles ψ allow us to simulate the X-ray powder diffraction data. For the (202)/(022) pair the values were averaged over the interval $0^\circ < \psi < 180^\circ$ since the two-fold symmetry persists. For the (311)/(131) pair the averaging was performed over $0^\circ < \psi < 360^\circ$. The parameters of the resolution function were fitted to the experimental data at $T > T_Q$ and $H = 0$. Different parameter sets were used for the (311)/(131) and (202)/(022) pairs, and the intensity parameter had to be adjusted to match the data at low temperature and high field.

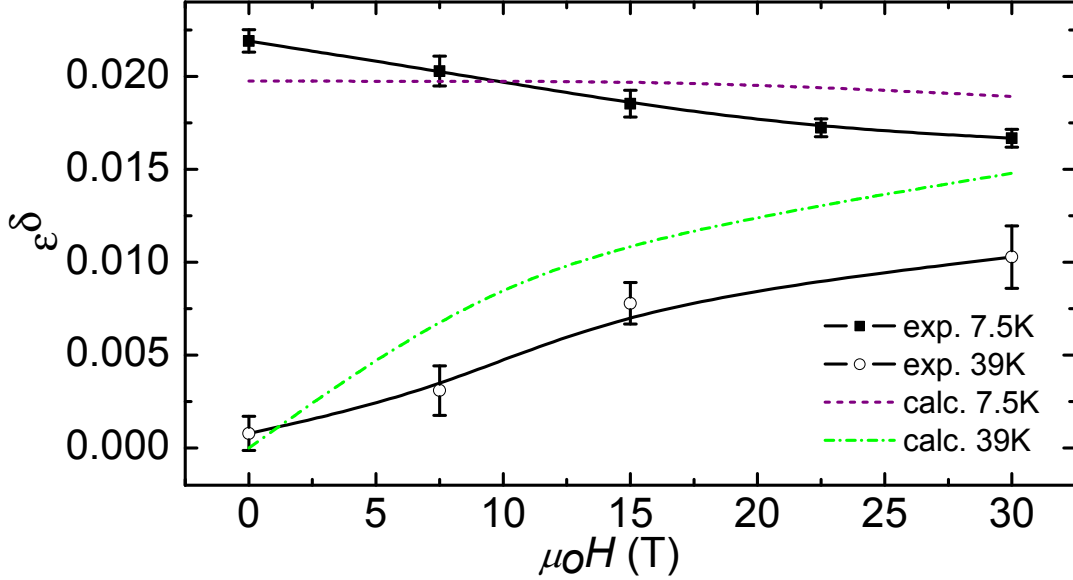


FIG. 4: Average order parameter as function of applied magnetic field for selected temperatures. Continuous lines: Experimental data. Dashed lines: Theory

At $T > T_Q$, calculations for the (202)/(022) pair adequately reproduce the almost symmetric splitting of the line by the magnetic field observed in the data (Fig. 3). The calculated magnitude of the splitting, however, is $\approx 25\%$ larger than the experimental one (Fig. 4). The origin of this discrepancy remains unclear. In particular, it does not seem to be related to the value of the interaction parameters used in the calculations since the value of the spontaneous splitting at $H = 0$ is correctly described (Fig. 4). Similar deviations between theory and experiment are observed at the (311)/(131) pair. Calculations describe the shape of the (311) line in different fields: the intensity ratio for two components of the split peak is about 1:2. But again the calculated value of the splitting is larger than the experimental one by about 25% (see Fig. 3). The OP may be decreased by sample heating, e.g. due to the magneto-caloric effect. A reasonable temperature increase of about 8–10 K, however, cannot fully explain the observed discrepancy.

The experimental observations at $T > T_Q$ and $H = 30$ T are well described by our calculations when the coefficient B^δ/C_0^δ is reduced by 25%; this value, however, is too small for the spontaneous deformation. This may be interpreted as the variation of the quadrupolar

constant G^δ under high magnetic field, as was observed for the quadrupolar constant G^γ of DyVO_4 and considered within an improved "compressible Ising model" [21, 22]. However for TbVO_4 no dependence of G^δ was observed when the OP increases as the temperature decreases, and its low field behavior is described adequately by the mean field theory [4].

For the quadrupole ordered phase the results of the numerical calculations for the (202) and (311) peaks are compared with the experimental data in Fig. 3. For both peaks the averaging were performed for two domains (ϵ^δ and $-\epsilon^\delta$) for $0 < \psi < 360^\circ$, in steps of $\Delta\psi = 5^\circ$. For the (202)/(022) pair the calculations do not reveal a noticeable decrease of the splitting under external field of 30 T, while for the (311)/(131) pair a small shift is expected for the low-angle component.

We examined, and refuted, several possible explanations for the discrepancy between the theoretical and experimental results. Firstly we ascertained that various weak pair interactions (bilinear, quadrupole of γ -, α - and ϵ - symmetry) which were omitted in our calculations do not change the results noticeably. Then we estimated the effect of the sample heating due to the magnetocaloric effect in our experiment. In the adiabatic regime, the temperature change is large enough (about 25 K at 7.5 K) for the magnetic field orientation close to the easy magnetization axis. Additional studies are necessary to elucidate the influence of the magnetocaloric effect in our experiments.

In summary, we have directly observed for the first time the effect of magnetic fields on the Jahn-Teller distortion of TbVO_4 , and compared the experimental data to a detailed mean field theory. Due to the polycrystalline nature of the sample and its strong MC anisotropy the calculated spectra had to be averaged over all possible orientations of the powder grains relative to the applied magnetic field. The applied magnetic field was found to influence both the magnitude of the OP, as observed in the splitting of the (311)/(131) and (202)/(022) pairs of Bragg peaks, and the relative domain populations, reflected in the intensity ratio between the partners of a pair. Our theory is in qualitative agreement with the experimental results, even though small quantitative discrepancies persist.

This new technique was found to be a powerful tool to study JT systems, and allows us to observe new aspects of magnetic behavior of the classical and well studied JT compound TbVO_4 . These high magnetic field data may be used both to revise known theoretical models and to develop new, improved ones.

The authors acknowledge the NWO/FWO Vlaanderen and ESRF for granting the beam-

time for these experiments, and thank the staff of DUBBLE CRG and the ESRF for help in setting up these experiments. We thank M. Nardone, J. Billette, and A. Zitouni for their excellent work on the pulsed field coil and cryostat. Ames Laboratory is supported by the Department of Energy, Office of Science under Contract No. W-7405-Eng-82. Z. A. K. acknowledges financial support from the RFBR (project No. 07-02-01043). Part of this research was funded by the ANR (ANR-05-BLAN-0238) and EuroMagNet (EU contract 506239).

-
- [1] E. Dagotto, Nanoscale Phase Separation and Colossal Magnetoresistance: The Physics of Manganites and Related Compounds, vol. 136 of Springer Series in Solid-State Sciences (Springer, 2003).
- [2] N. Hur, S. Park, P. A. Sharma, J. S. Ahn, S. Guha, and S.-W. Cheong, *Nature* **429**, 392 (2004).
- [3] L. C. Chapon, G. R. Blake, M. J. Gutmann, S. Park, N. Hur, P. G. Radaelli, and S.-W. Cheong, *Phys. Rev. Lett.* **93**, 177402 (2004).
- [4] G. A. Gehring and K. A. Gehring, *Rep. Prog. Phys.* **38**, 1 (1975).
- [5] B. W. Mangum, J. N. Lee, and H. W. Moos, *Phys. Rev. Lett.* **27**, 1517 (1971).
- [6] J. Sivardière and M. Blume, *Phys. Rev. B* **5**, 1126 (1972).
- [7] J. Sivardière, *Phys. Rev. B* **6**, 4284 (1972).
- [8] A. A. Demidov and N. P. Kolmakova, *Physica B* **363**, 245 (2005).
- [9] Z. A. Kazei, V. V. Snegirev, J.-M. Broto, and H. Rakoto, *JETP Letters* **82**, 609 (2005).
- [10] E. Pytte, *Phys. Rev. B* **9**, 932 (1974).
- [11] R. T. Hartley, C. H. Perry, and W. Richter, *J. Phys. C* **10**, L187 (1977).
- [12] V. I. Kut'ko and M. I. Kobets, *Czech J. Phys.* **46**, 2555 (1996).
- [13] K. Kirschbaum, A. Martin, D. A. Parrish, and A. A. Pinkerton, *J. Phys.: Condens. Matt.* **11**, 4483 (1999).
- [14] Y. Matsuda, Y. Ueda, H. Nojiri, T. Takahashi, T. Inami, K. Ohwada, Y. Murakami, and T. Arima, *Physica B* **346–347**, 519 (2004).
- [15] Y. Narumi, K. Kindo, K. Katsumata, M. Kawauchi, C. Broennimann, U. Staub, H. Toyokawa, Y. Tanaka, A. Kikkawa, T. Yamamoto, et al., *J. Syn. Rad.* **13**, 271 (2006).
- [16] P. Frings, J. Vanacken, C. Detlefs, F. Duc, J. E. Lorenzo, M. Nardone, J. Billette, A. Zitouni, W. Bras, and G. L. J. A. Rikken, *Rev. Sci. Instr.* **77**, 63903 (2006).

- [17] W. Bras, I. P. Dolbnya, D. Detollenaere, R. van Tol, M. Malfois, G. N. Greaves, A. J. Ryan, and E. Heeley, *J. Appl. Cryst.* **36**, 791 (2003).
- [18] S. H. Smith and B. M. Wanklyn, *J. Crystal Growth* **21**, 23 (1974).
- [19] B. M. Wanklyn, *J. Crystal Growth* **43**, 336 (1978).
- [20] Z. A. Kazei, N. P. Kolmakova, and O. A. Shishkina, *Physica B* **245**, 164 (1998).
- [21] A. A. Demidov, Z. A. Kazei, N. P. Kolmakova, J.-M. Broto, and H. Rakoto, *Phys. Rev. B* **70**, 134432 (2004).
- [22] J. H. Page, S. R. P. Smith, D. R. Taylor, and R. T. Hartley, *J. Phys. C* **12**, L875 (1979).
- [23] Note that for consistency with the existing literature [8, 9] we have defined the quadrupole operator P_{xy} in the high-temperature, tetragonal coordinate system. In the low-temperature, orthorhombic basis $\epsilon^\delta \propto \langle O_2^2 \rangle$, with $O_2^2 = J_x^2 - J_y^2$.