



HAL
open science

Tiling models for metadislocations in AlPdMn approximants

Michael Engel, Hans-Rainer Trebin

► **To cite this version:**

Michael Engel, Hans-Rainer Trebin. Tiling models for metadislocations in AlPdMn approximants. Philosophical Magazine, 2006, 86 (06-08), pp.979-984. 10.1080/14786430500255211 . hal-00513574

HAL Id: hal-00513574

<https://hal.science/hal-00513574>

Submitted on 1 Sep 2010

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Tiling models for metadislocations in AIPdMn approximants

Journal:	<i>Philosophical Magazine & Philosophical Magazine Letters</i>
Manuscript ID:	TPHM-05-May-0179.R1
Journal Selection:	Philosophical Magazine
Date Submitted by the Author:	21-Jun-2005
Complete List of Authors:	Engel, Michael; Universität Stuttgart, Institut für Theoretische und Angewandte Physik Trebin, Hans-Rainer; Universität Stuttgart, Institut für Theoretische und Angewandte Physik
Keywords:	quasicrystalline alloys, geometry, dislocation structures, approximants
Keywords (user supplied):	complex metallic alloys



Tiling models for metadislocations in AlPdMn approximants

M. Engel* and H.-R. Trebin

Institut für Theoretische und Angewandte Physik, Universität Stuttgart,
Pfaffenwaldring 57, D-70550 Stuttgart, Germany

June 21, 2005

Abstract

The AlPdMn quasicrystal approximants ξ , ξ' , and ξ'_n of the 1.6 nm decagonal phase and R , T , and T_n of the 1.2 nm decagonal phase can be viewed as arrangements of cluster columns on two-dimensional tilings. We substitute the tiles by Penrose rhombs and show, that alternative tilings can be constructed by a simple cut and projection formalism in three dimensional hyperspace. It follows that in the approximants there is a phasonic degree of freedom, whose excitation results in the reshuffling of the clusters. We apply the tiling model for metadislocations, which are special textures of partial dislocations.

1 Introduction

A quasiperiodic structure can be described as a cut through a hyperlattice decorated with atomic surfaces. As a consequence the atoms are arranged in a finite number of different local environments frequently leading to a substructure of highly symmetric clusters. The cluster positions can again be modelled by a simpler decoration consisting in the simplest case of exactly one atomic surface (for the cluster centre) per hyperlattice unit cell. The displacement of the cut space (phasonic displacement) is a discrete degree of freedom, called phasonic degree of freedom. It can be excited locally, leading to a rearrangement of the clusters by correlated atomic jumps. This view is supported by recent diffraction data of coherent phason modes in i(cosahedral)-AlPdMn (Coddens et al. 1999, Francoual et al. 2003) and by in situ observations of phason jumps via high-resolution transmission electron microscopy (HRTEM) in d(ecagonal)-AlCuCo (Edagawa et al. 2002).

The cut formalism cannot be applied directly if there is a gradient in the phasonic displacement. This is exemplified by the extreme case of a cut space running inbetween

* Author for correspondence. Email: mengel@itap.physik.uni-stuttgart.de

Figure 1: [Insert about here]

all atomic surfaces and not touching any of them. Hence we resort to another method: We substitute the atomic surfaces by atomic hypervolumes (Engel and Trebin 2005) of the same dimension as the hyperspace. For the construction two different spaces are needed: Those atomic hypervolumes that are cut by the (possibly deformed) cut space E_{Cut} are selected. The centre of each selected atomic hypervolume is projected onto the projection space E_{Proj} . By shearing the cut space, i.e. by introducing a linear phasonic displacement, periodic approximants are created. Phasonic degrees of freedom also can exist in these and play a fundamental role for phase transitions (Edagawa et al. 2004).

Here we discuss linear defects, metadislocations, in the phasonic degree of freedom for approximants of the AlPdMn system. This system is especially adequate for the examination of phasonic degrees of freedom since a stable i-phase, a stable 1.2 nm d-phase, a metastable 1.6 nm d-phase (which is assumed to be a solid solution of Mn in d-AlPd (Steurer 2004)), and a large variety of approximants have been observed in the phase diagram (Klein et al. 2000). All of them, as well as several binary AlPd and AlMn quasicrystals and approximants are related structurally.

2 Tiling models

A hyperspace model for i-AlPdMn has been proposed by Katz and Gratias (1993). It uses a six dimensional face-centred hyperlattice F^{6D} with lattice constant $2l^{6D} = 1.29$ nm and serves as a starting point since to our knowledge all newer, more complicated hyperspace models are refinements. It has been shown, that the approximants ξ and ξ' (Beraha et al. 1997) of the 1.6 nm d-phase and the approximants R and T (Beraha et al. 1998) of the 1.2 nm d-phase are described on an atomistic level by a shear in this model. However the authors had to introduce an additional mirror symmetry to assure full tenfold symmetry. The main building units are Mackay-type clusters, whose centres are projected from the hyperspace by using one atomic surface per hyperlattice unit cell. It is a subset of a triacontahedron, deflated by $\tau = \frac{1}{2}(\sqrt{5} + 1)$ with respect to the canonical triacontahedron, which is the projection of the hypercube with edge length l^{6D} on the orthogonal complement of E_{Proj} . The distance of the cluster centres is the shortest projection of neighboring F^{6D} -sites $e_i \pm e_j$ multiplied by the deflation factor: $t^{6D} = \frac{1}{5}\sqrt{10}\sqrt{\tau + 2}l^{6D} \simeq 0.78$ nm.

The relation of the approximants to the i-phase is given by two consecutive shears of E_{Cut} in the hyperspace: The first shear changes the cluster arrangement in direction of a fivefold axis e_1 . Together with the introduction of a mirror plane this results in a decagonal quasicrystal. The clusters are then aligned in columns parallel to the tenfold axis, so that the structures can be described by two-dimensional tilings, which are the projections in the column direction. The second shear rearranges the columns perpendicular to e_1 . We will now consider the tilings for the 1.6 nm and the 1.2 nm phases separately.

Neighboring clusters in the 1.6 nm d-phase and its approximants lie on planes per-

pendicular to \mathbf{e}_1 . Thus the tile length is t^{6D} as defined above. The ξ - and the ξ' -phase are built from flattened hexagons (H) arranged in parallel and in alternated orientation respectively. By introducing additional rows of pentagons (P) and nonagons (N) between each $n - 1$ rows of alternated Hs in the ξ' -phase we obtain the ξ'_n -phases. Such a PN-row is called a phason plane, which is justified since it is elongated in the \mathbf{e}_1 direction. As we will see, phason planes play an important role for the cluster reshuffling resulting from an excitation of the phasonic degree of freedom. Further tiles, the decagon (D) and an U-shaped tile (U) are observed in the 1.6 nm d-phase (Fig. 1 (a)).

Neighboring clusters in the 1.2 nm d-phase and its approximants lie on two planes staggered perpendicular to \mathbf{e}_1 with distance $\frac{1}{5}\sqrt{10}l^{6D} \simeq 0.41$ nm. The resulting tile length is $t^{6D} = \frac{1}{5}\sqrt{10}\tau l^{6D} \simeq 0.66$ nm. The R - and the T -phase are built from elongated hexagons (H') arranged in parallel and in alternated orientation respectively. The T_n -phases are created by introducing into the T -phase additional rows of boat-shaped tiles (B') between each n rows of alternated H's. A B'-row is again called a phason-plane. For the 1.2 nm d-phase additionally a decagon (D') and a star-shaped tile (S') are needed (Fig. 1 (b)).

By substituting the H, P, N, H', and B' tiles with acute rhombs (AR), (AR') and obtuse rhombs (OR), (OR') as shown in Fig. 1 (c) we obtain new tilings for the approximants, which can be interpreted as approximants of the Penrose-tiling. An H is substituted by an OR, while a phason plane corresponds to a combination of an AR-row and an OR-row. So the ξ'_n -phase has n OR-rows inbetween neighboring AR-rows. Similarly the T_n -phase has n AR-rows inbetween neighboring phason planes, represented by OR-rows. The rhombs occurring in the new tilings for the Ξ -approximants (ξ , ξ' , ξ'_n), as well as for the T -approximants (R , T , T_n) both only need three of the five basis vectors of the Penrose-tiling to be constructed. Therefore the tilings can be modelled in a simple three-dimensional hyperspace with the \mathbb{Z}^3 -lattice and lattice constant $l^{3D} = \tau\sqrt{\tau+2}l^{6D} \simeq 1.99$ nm. The projection matrices are ($s_i = \sin(2\pi\frac{i}{5})$, $c_i = \cos(2\pi\frac{i}{5})$):

$$\pi_{\Xi}^{\parallel} = \frac{1}{5}\sqrt{10} \begin{pmatrix} s_0 & s_1 & s_4 \\ c_0 & c_1 & c_4 \end{pmatrix}, \quad \pi_T^{\parallel} = \frac{1}{5}\sqrt{10} \begin{pmatrix} s_0 & s_2 & s_3 \\ c_0 & c_2 & c_3 \end{pmatrix}, \quad (1)$$

leading to an edge length of the tiles: $t^{3D} = \frac{1}{5}\sqrt{10}l^{3D} \simeq 1.26$ nm. There is one atomic hypervolume per unit cell, which is just the unit cell, and one phasonic degree of freedom. This three-dimensional hyperspace is the simplest model for a phasonic degree freedom besides the Fibonacci-chain.

3 Metadislocations

In the formalism of atomic hypervolumes a dislocation can be introduced into a tiling by a generalised Volterra process (Engel and Trebin 2005). It is uniquely characterised by a translation vector of the hyperlattice, the Burgers vector \mathbf{b} (here: $\mathbf{b}^{3D} = (b_1, b_2, b_3)$, $b_i \in \mathbb{Z}$), that splits up into a phononic component $\mathbf{b}^{\parallel} = \pi^{\parallel}\mathbf{b}$ (deforming the tiles) and a phasonic component \mathbf{b}^{\perp} (rearranging the tiles). The latter can only be calculated from the full six-dimensional Katz-Gratias model. If it is not zero, such a dislocation is a partial dislocation.

Figure 2: [Insert about here]

By (i) extending the linear theory of elasticity to the hyperspace, (ii) approximating the phasonic degree as continuous, and (iii) assuming isotropy in the strain fields, the line energy E of a dislocation is expressed as:

$$E = c_{\text{phon}} \|\mathbf{b}^{\parallel}\|^2 + c_{\text{phas}} \|\mathbf{b}^{\perp}\|^2 + c_{\text{coupl}} \|\mathbf{b}^{\parallel}\| \|\mathbf{b}^{\perp}\|. \quad (2)$$

Besides a phononic contribution with material constant c_{phon} and a phasonic contribution with c_{phas} , a coupling term is present with c_{coupl} . According to experiment we assume $c_{\text{phon}} \gg c_{\text{phas}} \approx c_{\text{coupl}}$. Since stable dislocations are those with the lowest energy, we have to minimise $\|\mathbf{b}^{\parallel}\|$. We will discuss this in parallel for dislocations in the Ξ - and the T -approximants. The minimization yields $b_2 = b_3$ in both cases. Furthermore we have $b_1 = -\tau^{-1}b_2$ for \mathbf{b}_{Ξ}^{3D} and $b_1 = \tau b_2$ for \mathbf{b}_T^{3D} . Here we approximate τ^{-1} by the fractions F_{m-1}/F_m and τ by the fractions F_{m+1}/F_m respectively. $(F_m)_{m \in \mathbb{N}}$ are the Fibonacci numbers with start values $F_1 = F_2 = 1$. Finally the Burgers vectors of stable dislocations are: $\mathbf{b}_{\Xi}^{3D} = (F_{m-1}, -F_m, -F_m)$ and $\mathbf{b}_T^{3D} = (F_{m+1}, F_m, F_m)$. Interestingly they correspond to the same six-dimensional Burgers vectors:

$$\mathbf{b}_{\Xi}^{6D} = \mathbf{b}_T^{6D} = (0, 0, -F_{m-2}, F_{m-1}, F_{m-2}, F_{m-1}). \quad (3)$$

Hence it suffices to consider both cases together for the rest of our calculations. The phononic component $\mathbf{b}^{\parallel} = \mathbf{b}_{\Xi}^{\parallel} = \mathbf{b}_T^{\parallel}$ is perpendicular to the phason-planes (pointing in the vertical direction in Fig. 1). We get $\|\mathbf{b}^{\parallel}\| = \tau^{-m}t^{3D}$ and $\|\mathbf{b}^{\perp}\| = \tau^{m-3}t^{3D}$. Substituting this into (2), we have $E = [c_{\text{phon}}\tau^{-2m+3} + c_{\text{phas}}\tau^{2m-3} + c_{\text{coupl}}] \tau^{-3}(t^{3D})^2$. There is a minimum for $c_{\text{phon}}/c_{\text{phas}} = \tau^{4m-6}$. This determines the Burgers vector with lowest energy for given values for the material constants c_{phon} and c_{phas} . However it has to be noted that these are not necessarily identical for the Ξ - and the T -approximants.

Tilings of the ξ'_3 - and the T_3 -phase with $m = 4$ dislocations have been calculated (Fig. 2). They show large rearrangements of the tiles due to the phasonic component \mathbf{b}^{\perp} and negligible deformations of the tiles due to the smaller phononic component \mathbf{b}^{\parallel} . The dislocations are also dislocations in the metastructure of the phason planes. Therefore Klein et al. (1999), who discovered these dislocations in HRTEM images of the ξ'_2 -phase, named them metadislocations. The fact, that the experimentally most often observed metadislocations are those with $m = 4$ suggests $c_{\text{phon}}/c_{\text{phas}} = \tau^{10} \simeq 123$. We do not know of Burgers vector determinations or observations of metadislocations in the T -approximants, but dislocations with the Burgers vectors (3) are also the ones most often observed in the i -phase (Rosenfeld et al. 1995).

4 Discussion and conclusion

In the ξ'_n - and the T_n -phases the phasonic degree of freedom is related to the movement of the phason planes. Since there are no phason planes in the ξ -, ξ' -, R -, and T -phase,

1
2
3
4
5
6
7 the phasonic degree of freedom cannot be excited locally. However metadislocations can
8 exist in the ξ' - and the T -phase, but not in the ξ - and the R -phase. It can be shown, that
9 there is no consistent way to introduce dislocations with phasonic components in the latter
10 phases.
11

12 A motion of the metadislocation (like the motion of any dislocation in a quasicrystal
13 or large unit cell approximant) is necessarily accompanied by diffusion in the form of tile
14 rearrangements. The motion is possible by climb in direction of the phason planes or by
15 glide perpendicular to them. During the climb motion new phason planes are created (or
16 dissolved) behind the dislocation core. A large number of metadislocations moving through
17 the ξ' - or T -phase could even lead to a phase transformation to the ξ'_n - or T_n -phases making
18 the phasonic degree of freedom continuously excitable. This is affirmed by HRTEM images
19 of phase boundaries between the ξ' - and the ξ'_2 -phase formed by metadislocations (Heggen
20 and Feuerbacher 2005).
21
22


23 On the other side, glide motion does not change the number of phason planes. At least
24 in the ξ' - and the T -phase glide motion seems unprobable, since the phason planes running
25 out of the dislocation core would have to be dragged along, while climb motion only needs
26 a reconstruction of the tiling near the dislocation core. (Similar arguments leading to the
27 same conclusion, as well as newer experimental work are presented in Feuerbacher and
28 Heggen (2005).) We have to note, that there are no direct observations of metadislocation
29 motion in approximants yet, although in the i -phase dislocations with identical Burgers
30 vectors have been shown by in-situ observations to move by climb (Momprou et al. 2004).
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

References


- 1
2
3
4
5
6
7
8
9 BERAHA, L., DUNEAU, M., KLEIN, H., and AUDIER, M., 1997, *Phil. Mag. A*, **76**, 587.
10
11 BERAHA, L., DUNEAU, M., KLEIN, H., and AUDIER, M., 1998, *Phil. Mag. A*, **78**, 345.
12
13 CODDENS, G., LYONNARD, S., HENNION, B., and CALVAYRAC, Y., 1999, *Phys. Rev.*
14 *Lett.*, **83**, 3226.
15
16 EDAGAWA, K., MANDAL, P., HOSONO, K., SUZUKI, K., and TAKEUCHI, S., 2004, *Phys.*
17 *Rev. B*, **70**, 184202.
18
19 EDAGAWA, K., SUZUKI, K., and TAKEUCHI, S., 2002, *J. All. Comp.*, **342**, 271.
20
21 ENGEL, M., and TREBIN, H.-R., 2005, *Phil. Mag.*, in press.
22
23 FEUERBACHER, M., and HEGGEN, M., 2005, *Phil. Mag.*, this volume.
24
25 FRANCOUAL, S., LIVET, F., DE BOISSIEU, M., YAKHOU, F., BLEY, F., LETOU-
26 BLON, A., CAUDRON, R., and GASTALDI, J., 2003, *Phys. Rev. Lett.*, **91**, 225501.
27
28 KATZ, A., and GRATIAS, G., 1993, *Journ. Non-Cryst. Solids*, **153-154**, 187.
29
30 KLEIN, H., DURAND-CHARRE, M., and AUDIER, M., 2000, *J. All. Comp.*, **296**, 128.
31
32 KLEIN, H., FEUERBACHER, M., SCHALL, P., and URBAN, K., 1999, *Phys. Rev. Lett.*,
33 **82**, 3468.
34
35 HEGGEN, M., and FEUERBACHER, M., 2005, *Phil. Mag.*, this volume.
36
37 MOMPIOU, F., CAILLARD, D., and FEUERBACHER, M., 2004, *Phil. Mag.*, **84**, 2777.
38
39 ROSENFELD, R., FEUERBACHER, M., BAUFELD, B., BARTSCH, M., WOLLGARTEN, M.,
40 HANKE, G., BEYSS, M., MESSERSCHMIDT, U., and URBAN, K., 1995, *Phil. Mag.*
41 *Lett.*, **72**, 375.
42
43
44
45 STEURER, W., 2004, *Z. Kristallogr.*, **219**, 391.
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Figure captions


1. Calculated tilings for various approximants of the AlPdMn i-phase. (a) 1.6 nm phases: The tiling of the d-phase is the Tübingen Triangle Tiling (TTT). (b) 1.2 nm phases: The D' centres lie on a τ^2 inflated TTT. (c) The tiles can be substituted with Penrose rhomb tiles. The substitution is different for the 1.6 nm phases and the 1.2 nm phases.
2. Tilings of the ξ_3' - (left) and the T_3 -phase (right) with $m = 4$ metadislocations. $2F_m$ new phason planes are inserted from the left, ending at the triangular shaped dislocation core.

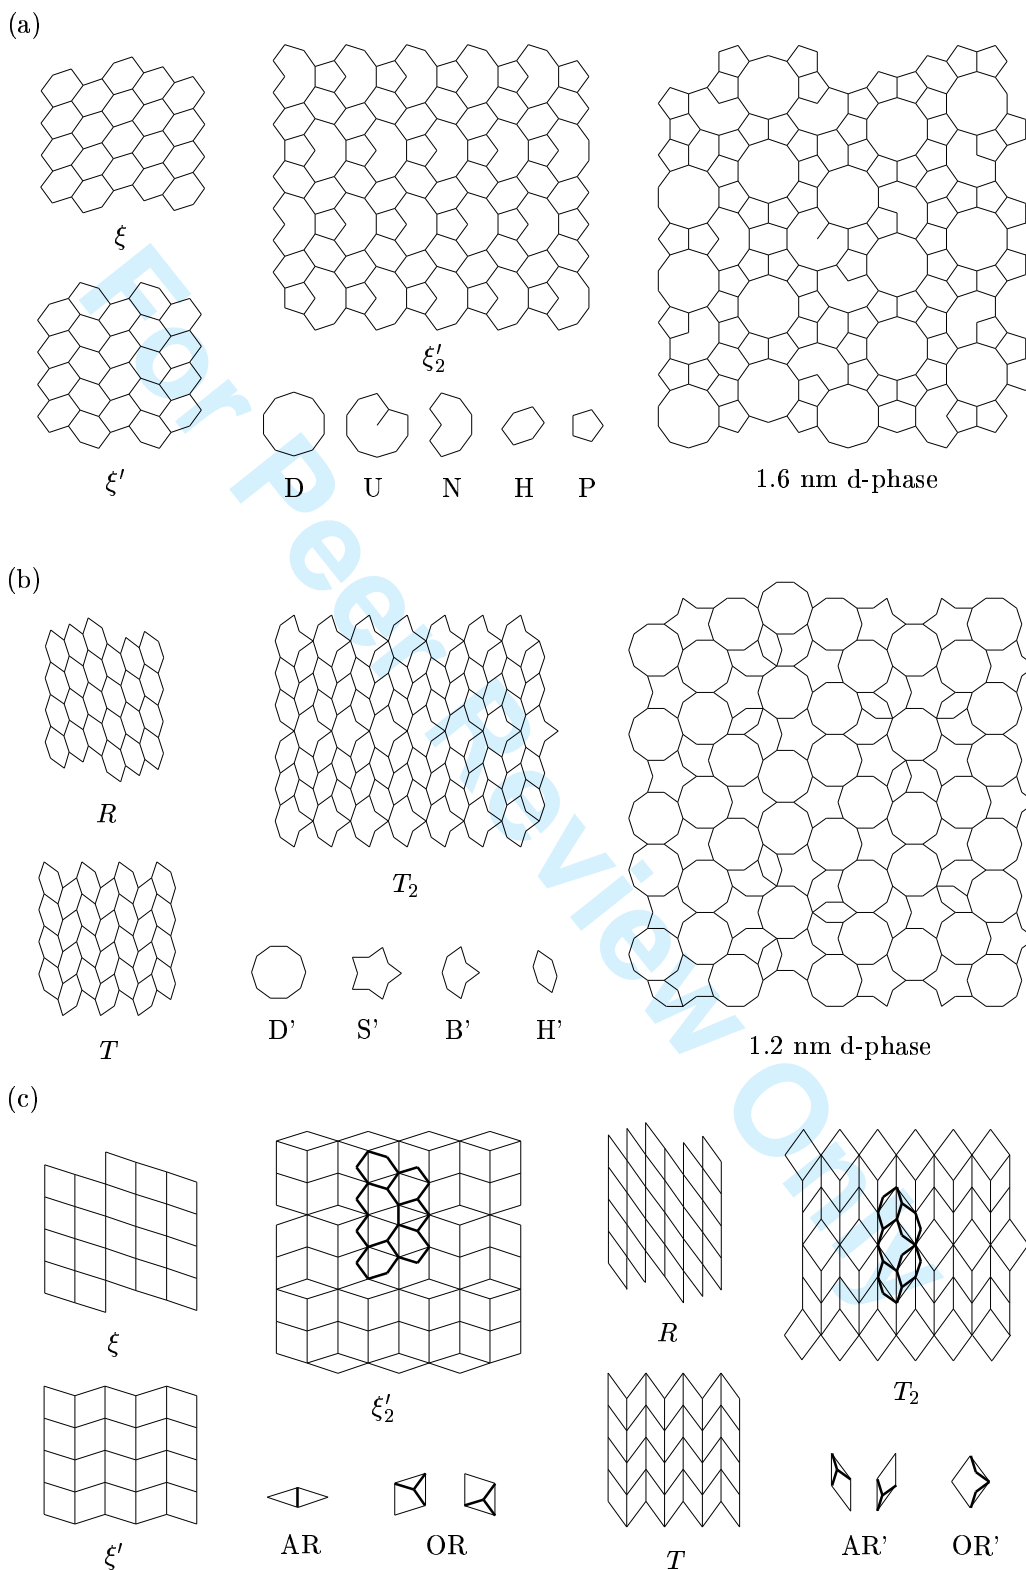

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

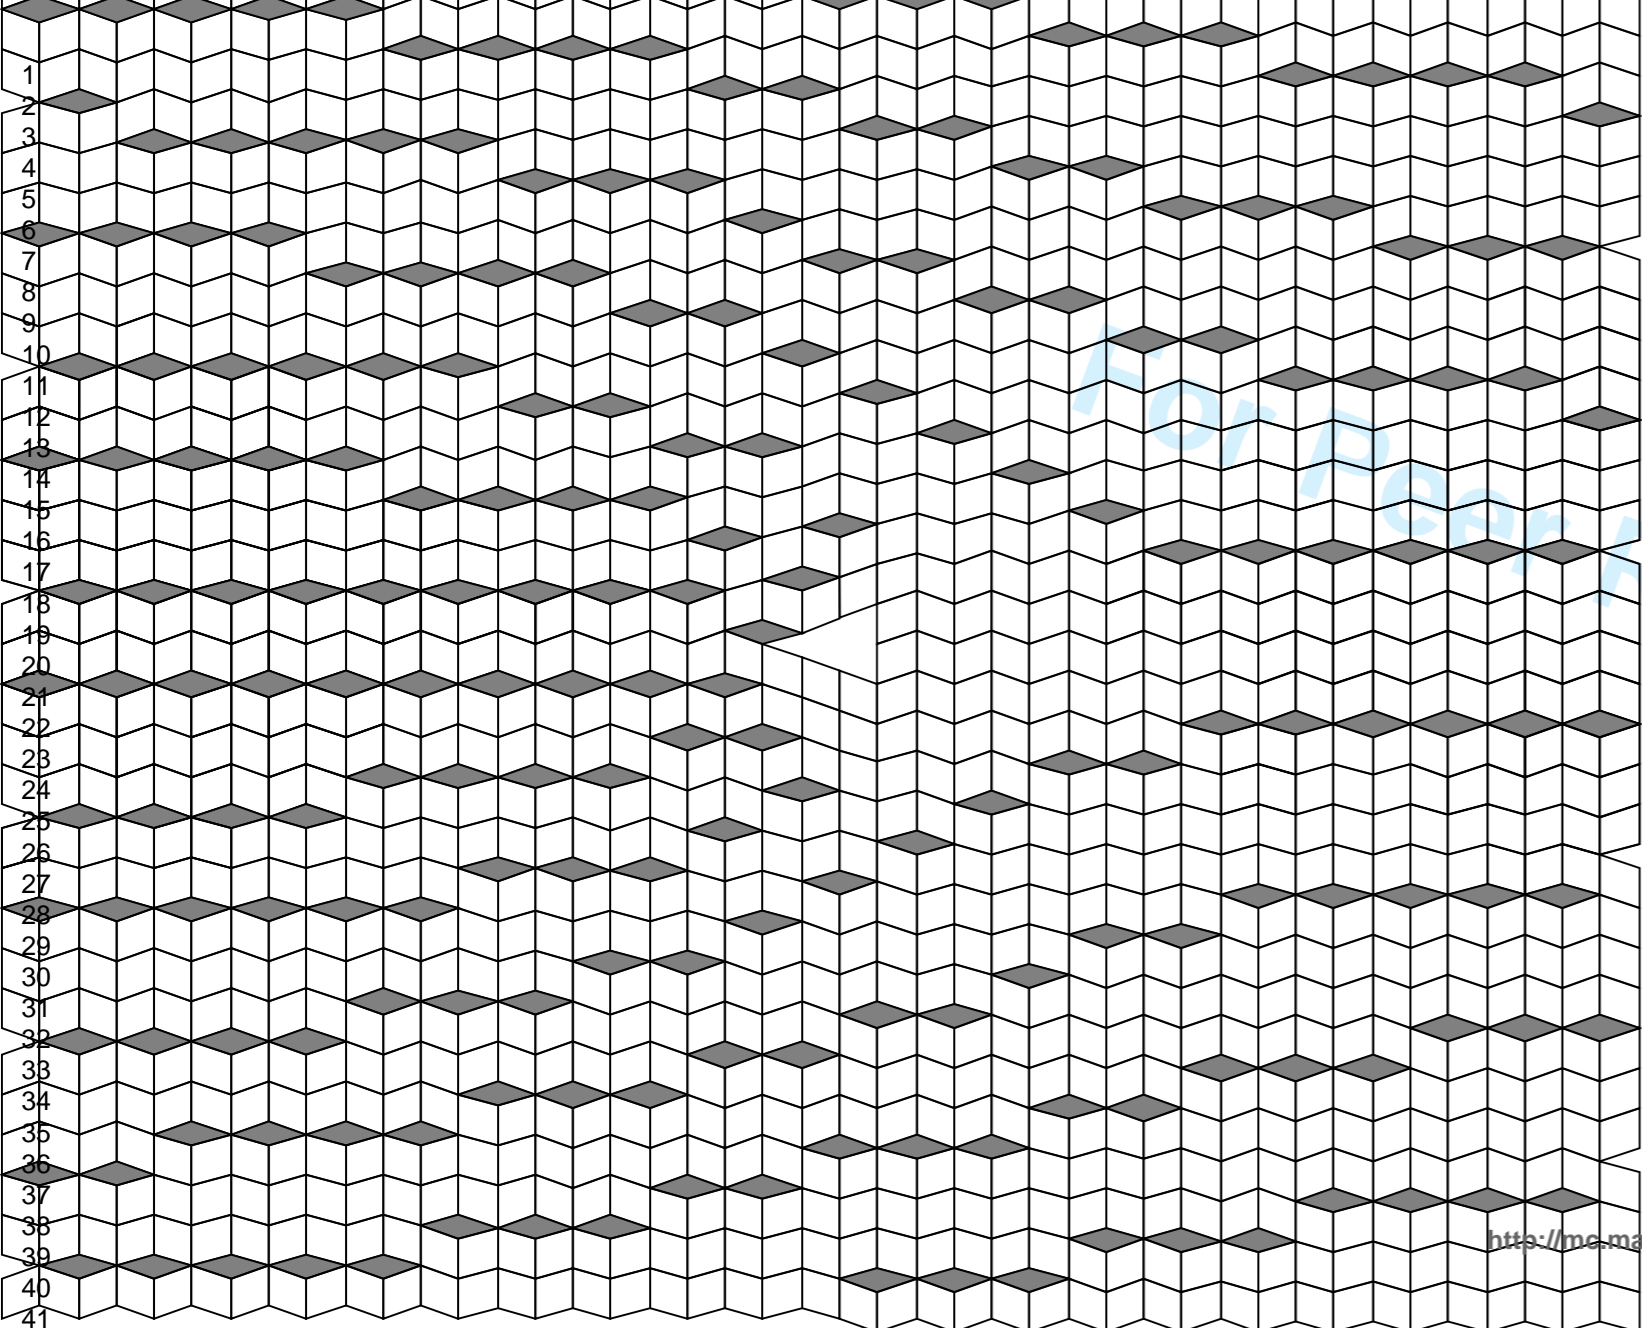

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41

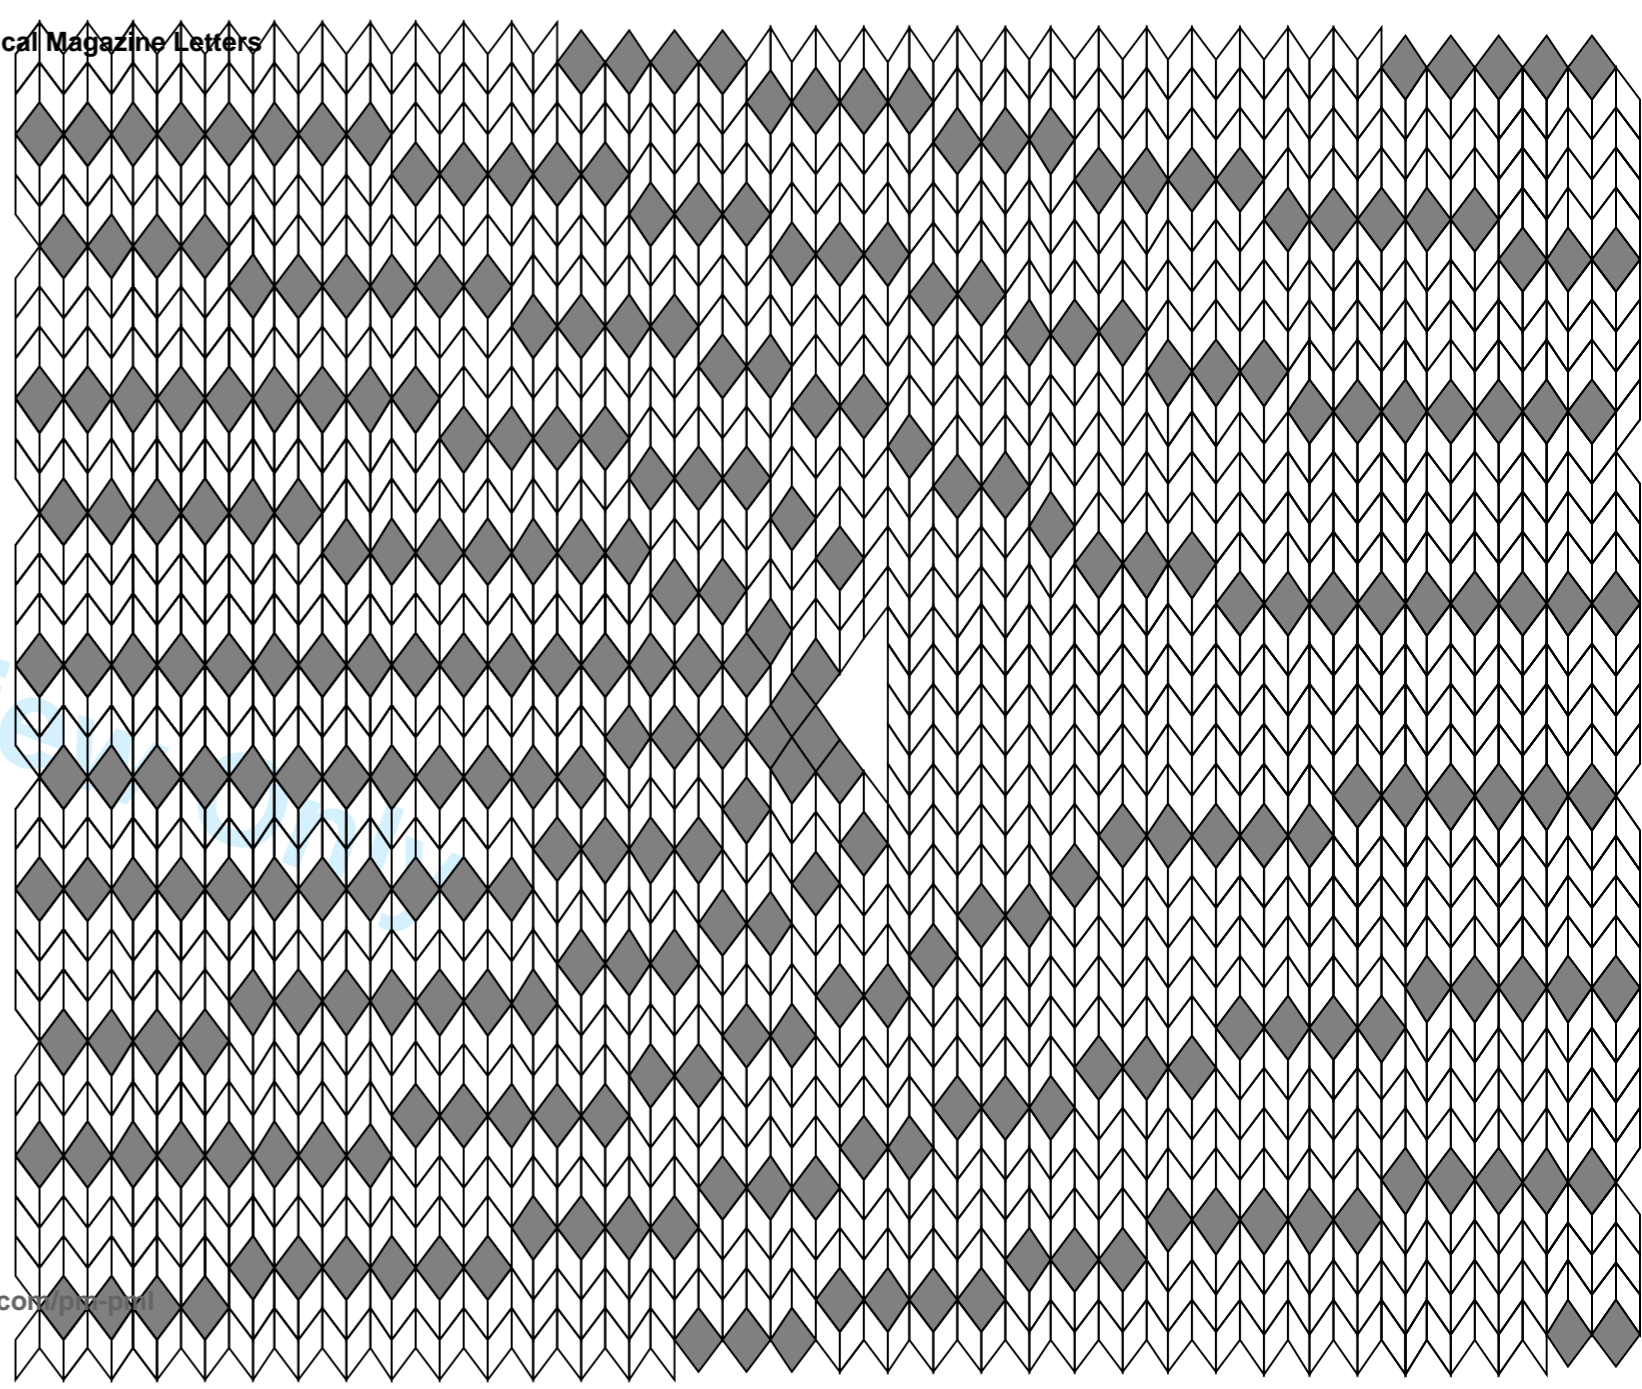

```

1
2
3 \documentclass[12pt]{article}
4
5 \usepackage{graphicx}
6 \usepackage{amsmath}
7 \usepackage{a4wide}
8 \usepackage{psfrag}
9 \usepackage{bbm}
10 \usepackage{natbib}
11
12 \newcommand{\ve}{\boldsymbol}
13 \bibpunct[,]{(}{)}{,}{a}{}{,}
14
15 \begin{document}
16
17 \title{Tiling models for metadislocations in AlPdMn approximants}
18
19 \author{M.~Engel\footnote{Author for correspondence. Email:
20 mengel@itap.physik.uni-stuttgart.de}~ and H.-R.~Trebin\
21 {\normalsize Institut f\"ur Theoretische und Angewandte Physik,}
22 {\normalsize Universit\"at Stuttgart,} \
23 {\normalsize Pfaffenwaldring 57, D-70550 Stuttgart, Germany}\
24 }
25
26 \maketitle
27
28 \begin{abstract}
29
30 The AlPdMn quasicrystal approximants  $\xi$ ,  $\xi'$ , and  $\xi'_n$  of the
31 1.6~nm decagonal phase and  $R$ ,  $T$ , and  $T_n$  of the 1.2~nm decagonal phase
32 can be viewed as arrangements of cluster columns on two-dimensional
33 tilings. We substitute the tiles by Penrose rhombs and show, that alternative
34 tilings can be constructed by a simple cut and projection formalism in three
35 dimensional hyperspace. It follows that in the approximants there is a
36 phasonic degree of freedom, whose excitation results in the reshuffling of the
37 clusters. We apply the tiling model for metadislocations, which are special
38 textures of partial dislocations.
39
40 \end{abstract}
41
42
43 \section{Introduction}
44
45 A quasiperiodic structure can be described as a cut through a hyperlattice
46 decorated with atomic surfaces. As a consequence the atoms are arranged in a
47 finite number of different local environments frequently leading to a
48 substructure of highly symmetric clusters. The cluster positions can again be
49 modelled by a simpler decoration consisting in the simplest case of exactly
50 one atomic surface (for the cluster centre) per hyperlattice unit cell. The
51 displacement of the cut space (phasonic displacement) is a discrete degree of
52 freedom, called phasonic degree of freedom. It can be excited locally, leading
53 to a rearrangement of the clusters by correlated atomic jumps. This view is
54 supported by recent diffraction data of coherent phason modes in
55 i(cosahedral)-AlPdMn \cite[{}]{itapdb:Coddens1999, itapdb:Francoual2003} and by
56 in situ observations of phason jumps via high-resolution transmission electron
57 microscopy (HRTEM) in d(ecagonal)-AlCuCo \cite[{}]{itapdb:Edagawa2002}.
58
59 The cut formalism cannot be applied directly if there is a gradient in
60 the phasonic displacement. This is exemplified by the extreme case of a cut
space running inbetween all atomic surfaces and not touching any of
them. Hence we resort to another method: We substitute the atomic surfaces by

```

atomic hypervolumes \cite[{}]{itapdb:Engel2005} of the same dimension as the hyperspace. For the construction two different spaces are needed: Those atomic hypervolumes that are cut by the (possibly deformed) cut space $E_{\{\text{Cut}\}}$ are selected. The centre of each selected atomic hypervolume is projected onto the projection space $E_{\{\text{Proj}\}}$. By shearing the cut space, i.e. by introducing a linear phasonic displacement, periodic approximants are created. Phasonic degrees of freedom also can exist in these and play a fundamental role for phase transitions \cite[{}]{itapdb:Edagawa2004}.

Here we discuss linear defects, metadislocations, in the phasonic degree of freedom for approximants of the AlPdMn system. This system is especially adequate for the examination of phasonic degrees of freedom since a stable i -phase, a stable 1.2~nm d -phase, a metastable 1.6~nm d -phase (which is assumed to be a solid solution of Mn in d -AlPd \cite[{}]{itapdb:steuerer2004}), and a large variety of approximants have been observed in the phase diagramm \cite[{}]{itapdb:Klein2000a}. All of them, as well as several binary AlPd and AlMn quasicrystals and approximants are related structurally.

\section{Tiling models}

A hyperspace model for i -AlPdMn has been proposed by \cite[{}]{itapdb:Katz1993}. It uses a six dimensional face-centred hyperlattice F^{6D} with lattice constant $t^{6D}=1.29\text{\AA}$ and serves as a starting point since to our knowledge all newer, more complicated hyperspace models are refinements. It has been shown, that the approximants ξ and ξ' \cite[{}]{itapdb:Beraha1997} of the 1.6~nm d -phase and the approximants R and T \cite[{}]{itapdb:Beraha1998} of the 1.2~nm d -phase are described on an atomistic level by a shear in this model. However the authors had to introduce an additional mirror symmetry to assure full tenfold symmetry. The main building units are Mackay-type clusters, whose centres are projected from the hyperspace by using one atomic surface per hyperlattice unit cell. It is a subset of a triacontahedron, deflated by $\tau=\frac{1}{2}(\sqrt{5}+1)$ with respect to the canonical triacontahedron, which is the projection of the hypercube with edge length l^{6D} on the orthogonal complement of $E_{\{\text{Proj}\}}$. The distance of the cluster centres is the shortest projection of neighboring F^{6D} -sites $\vec{e}_i \pm \vec{e}_j$ multiplied by the deflation factor: $t^{6D}=\frac{1}{5}\sqrt{10}\sqrt{\tau+2}l^{6D}\simeq 0.78\text{\AA}$.

The relation of the approximants to the i -phase is given by two consecutive shears of $E_{\{\text{Cut}\}}$ in the hyperspace: The first shear changes the cluster arrangement in direction of a fivefold axis \vec{e}_1 . Together with the introduction of a mirror plane this results in a decagonal quasicrystal. The clusters are then aligned in columns parallel to the tenfold axis, so that the structures can be described by two-dimensional tilings, which are the projections in the column direction. The second shear rearranges the columns perpendicular to \vec{e}_1 . We will now consider the tilings for the 1.6~nm and the 1.2~nm phases separately.

\begin{figure}
\caption{\bf[Insert about here] \label{fig:tilings}}
\end{figure}

Neighboring clusters in the 1.6~nm d -phase and its approximants lie on planes perpendicular to \vec{e}_1 . Thus the tile length is t^{6D} as defined above. The ξ - and the ξ' -phase are built from flattened hexagons (H) arranged in parallel and in alternated orientation respectively. By introducing additional rows of pentagons (P) and nonagons (N) between each n -1 rows of alternated Hs in the ξ' -phase we obtain the ξ'_n -phases. Such a PN-row is called a phason plane, which is justified

since it is elongated in the $\ve{e}_{\{1\}}$ direction. As we will see, phason planes play an important role for the cluster reshuffling resulting from an excitation of the phasonic degree of freedom. Further tiles, the decagon (D) and an U-shaped tile (U) are observed in the 1.6~nm d-phase (Fig.~\ref{fig:tilings} (a)).

Neighboring clusters in the 1.2~nm d-phase and its approximants lie on two planes staggered perpendicular to $\ve{e}_{\{1\}}$ with distance $\frac{1}{5}\sqrt{10}l^{\{6D\}}\simeq 0.41\text{\AA}$. The resulting tile length is $t^{\{6D\}}=\frac{1}{5}\sqrt{10}\tau l^{\{6D\}}\simeq 0.66\text{\AA}$. The $\$R\$$ - and the $\$T\$$ -phase are built from elongated hexagons (H') arranged in parallel and in alternated orientation respectively. The $\$T_{\{n\}}\$$ -phases are created by introducing into the $\$T\$$ -phase additional rows of boat-shaped tiles (B') between each $\$n\$$ rows of alternated H's. A B'-row is again called a phason-plane. For the 1.2~nm d-phase additionally a decagon (D') and a star-shaped tile (S') are needed (Fig.~\ref{fig:tilings} (b)).

By substituting the H, P, N, H', and B' tiles with acute rhombs (AR), (AR') and obtuse rhombs (OR), (OR') as shown in Fig.~\ref{fig:tilings} (c) we obtain new tilings for the approximants, which can be interpreted as approximants of the Penrose-tiling. An H is substituted by an OR, while a phason plane corresponds to a combination of an AR-row and an OR-row. So the $\$\xi_{\{n\}}\$$ -phase has $\$n\$$ OR-rows inbetween neighboring AR-rows. Similarly the $\$T_{\{n\}}\$$ -phase has $\$n\$$ AR-rows inbetween neighboring phason planes, represented by OR-rows. The rhombs occurring in the new tilings for the $\$\xi_{\{i\}}\$$ -approximants ($\$\xi_{\{i\}}\$$, $\$\xi_{\{i\}}'$, $\$\xi_{\{i\}}'_{\{n\}}\$$), as well as for the $\$T\$$ -approximants ($\$R\$$, $\$T\$$, $\$T_{\{n\}}\$$) both only need three of the five basis vectors of the Penrose-tiling to be constructed. Therefore the tilings can be modelled in a simple three-dimensional hyperspace with the $\mathbb{Z}^{\{3\}}$ -lattice and lattice constant $l^{\{3D\}}=\tau\sqrt{\tau+2}l^{\{6D\}}\simeq 1.99\text{\AA}$. The projection matrices are ($\$s_{\{i\}}=\sin(2\pi\frac{i}{5})\$$, $\$c_{\{i\}}=\cos(2\pi\frac{i}{5})\$$):

$$\begin{equation} \pi^{\{\parallel\}}_{\{\xi\}}=\frac{1}{5}\sqrt{10}\left(\begin{array}{ccc} s_{\{0\}} & s_{\{1\}} & s_{\{4\}} \\ c_{\{0\}} & c_{\{1\}} & c_{\{4\}} \end{array}\right), \quad \pi^{\{\parallel\}}_{\{T\}}=\frac{1}{5}\sqrt{10}\left(\begin{array}{ccc} s_{\{0\}} & s_{\{2\}} & s_{\{3\}} \\ c_{\{0\}} & c_{\{2\}} & c_{\{3\}} \end{array}\right), \end{equation}$$

leading to an edge length of the tiles:

$t^{\{3D\}}=\frac{1}{5}\sqrt{10}l^{\{3D\}}\simeq 1.26\text{\AA}$. There is one atomic hypervolume per unit cell, which is just the unit cell, and one phasonic degree of freedom. This three-dimensional hyperspace is the simplest model for a phasonic degree of freedom besides the Fibonacci-chain.

\section{Metadislocations}

In the formalism of atomic hypervolumes a dislocation can be introduced into a tiling by a generalised Volterra process \cite[{}]{itapdb:Engel2005}. It is uniquely characterised by a translation vector of the hyperlattice, the Burgers vector \ve{b} (here: $\ve{b}^{\{3D\}}=(b_{\{1\}},b_{\{2\}},b_{\{3\}})$, $\$b_{\{i\}}\in\mathbb{Z}\$$), that splits up into a phononic component $\ve{b}^{\{\parallel\}}=\pi^{\{\parallel\}}\ve{b}$ (deforming the tiles) and a phasonic component $\ve{b}^{\{\perp\}}$ (rearranging the tiles). The latter can only be calculated from the full six-dimensional Katz-Gratias model. If it is not zero, such a dislocation is a partial dislocation. By (i) extending the linear theory of elasticity to the hyperspace, (ii) approximating the phasonic degree as continuous, and (iii) assuming isotropy in the strain fields, the line energy $\$E\$$ of a dislocation is expressed as:

```

1
2
3 \begin{equation}\label{eq:energy}
4 E=c_{\text{phon}}|\ve{b}^{\parallel}|^2+c_{\text{phas}}|\ve{b}^{\perp}|^2+
5 c_{\text{coupl}}|\ve{b}^{\parallel}||\ve{b}^{\perp}|.
6 \end{equation}
7

```

Besides a phononic contribution with material constant c_{phon} and a phasonic contribution with c_{phas} , a coupling term is present with c_{coupl} . According to experiment we assume $c_{\text{phon}} \gg c_{\text{phas}} \approx c_{\text{coupl}}$. Since stable dislocations are those with the lowest energy, we have to minimise $|\ve{b}^{\parallel}|$. We will discuss this in parallel for dislocations in the ξ - and the T -approximants. The minimization yields $b_2 = b_3$ in both cases. Furthermore we have $b_1 = -\tau^{-1}b_2$ for \ve{b}^{3D}_{ξ} and $b_1 = \tau b_2$ for \ve{b}^{3D}_T . Here we approximate τ^{-1} by the fractions F_{m-1}/F_m and τ by the fractions F_{m+1}/F_m respectively. $(F_m)_N$ are the Fibonacci numbers with start values $F_1 = F_2 = 1$. Finally the Burgers vectors of stable dislocations are: $\ve{b}^{\text{3D}}_{\xi} = (F_{m-1}, -F_m, -F_m)$ and $\ve{b}^{\text{3D}}_T = (F_{m+1}, F_m, F_m)$. Interestingly they correspond to the same six-dimensional Burgers vectors:

```

23 \begin{equation}\label{eq:burgers}
24 \ve{b}^{\text{6D}}_{\xi} = \ve{b}^{\text{6D}}_T = (0, 0, -F_{m-2}, F_{m-1}, F_{m-2}, F_{m-1}).
25 \end{equation}

```

Hence it suffices to consider both cases together for the rest of our calculations. The phononic component $\ve{b}^{\parallel} = \ve{b}^{\parallel}_{\xi} = \ve{b}^{\parallel}_T$ is perpendicular to the phason-planes (pointing in the vertical direction in Fig.~\ref{fig:tilings}). We get $|\ve{b}^{\parallel}| = \tau^{-m}t^{\text{3D}}$ and $|\ve{b}^{\perp}| = \tau^{m-3}t^{\text{3D}}$. Substituting this into (\ref{eq:energy}), we have $E = \left[c_{\text{phon}} \tau^{-2m+3} + c_{\text{phas}} \tau^{2m-3} + c_{\text{coupl}} \right] \tau^{-3} (t^{\text{3D}})^2$. There is a minimum for $c_{\text{phon}}/c_{\text{phas}} = \tau^{4m-6}$. This determines the Burgers vector with lowest energy for given values for the material constants c_{phon} and c_{phas} . However it has to be noted that these are not necessarily identical for the ξ - and the T -approximants.

```

39 \begin{figure}
40 \caption{\bf[Insert about here] \label{fig:meta}}
41 \end{figure}
42

```

Tilings of the ξ_3 - and the T_3 -phase with $m=4$ dislocations have been calculated (Fig.~\ref{fig:meta}). They show large rearrangements of the tiles due to the phasonic component \ve{b}^{\perp} and negligible deformations of the tiles due to the smaller phononic component \ve{b}^{\parallel} . The dislocations are also dislocations in the metastructure of the phason planes. Therefore \cite{itapdb:Klein1999}, who discovered these dislocations in HRTEM images of the ξ_2 -phase, named them metadislocations. The fact, that the experimentally most often observed metadislocations are those with $m=4$ suggests $c_{\text{phon}}/c_{\text{phas}} = \tau^{10} \simeq 123$. We do not know of Burgers vector determinations or observations of metadislocations in the T -approximants, but dislocations with the Burgers vectors (\ref{eq:burgers}) are also the ones most often observed in the i -phase \cite{itapdb:Rosenfeld1995a}.

```

57 \section{Discussion and conclusion}
58

```

In the ξ_n - and the T_n -phases the phasonic degree of freedom is related to the movement of the phason planes. Since there are no phason planes in the ξ -, ξ' -, R -, and T -phase, the phasonic degree of freedom

cannot be excited locally. However metadislocations can exist in the ξ' - and the T -phase, but not in the ξ - and the R -phase. It can be shown, that there is no consistent way to introduce dislocations with phasonic components in the latter phases.

A motion of the metadislocation (like the motion of any dislocation in a quasicrystal or large unit cell approximant) is necessarily accompanied by diffusion in the form of tile rearrangements. The motion is possible by climb in direction of the phason planes or by glide perpendicular to them. During the climb motion new phason planes are created (or dissolved) behind the dislocation core. A large number of metadislocations moving through the ξ' - or T -phase could even lead to a phase transformation to the ξ'_n - or T_n -phases making the phasonic degree of freedom continuously excitable. This is affirmed by HRTEM images of phase boundaries between the ξ' - and the ξ'_2 -phase formed by metadislocations \cite[{}]{itapdb:Heggen2005}.

On the other side, glide motion does not change the number of phason planes. At least in the ξ' - and the T -phase glide motion seems unprobable, since the phason planes running out of the dislocation core would have to be dragged along, while climb motion only needs a reconstruction of the tiling near the dislocation core. (Similar arguments leading to the same conclusion, as well as newer experimental work are presented in \cite[{}]{itapdb:Feuerbacher2005}.) We have to note, that there are no direct observations of metadislocation motion in approximants yet, although in the i -phase dislocations with identical Burgers vectors have been shown by in-situ observations to move by climb \cite[{}]{itapdb:Momprou2004}.

\newpage

\begin{thebibliography}{20}

\bibitem[{}]{Beraha et al. (1997)}[{}]{itapdb:Beraha1997}

{\sc {Beraha},~L., {Duneau},~M., {Klein},~H.,} and {\sc {Audier},~M.},
 \newblock 1997, {\it Phil.\ Mag.}~A, {\bf 76}, 587.

\bibitem[{}]{Beraha et al. (1998)}[{}]{itapdb:Beraha1998}

{\sc {Beraha},~L., {Duneau},~M., {Klein},~H.,} and {\sc {Audier},~M.},
 \newblock 1998, {\it Phil.\ Mag.}~A, {\bf 78}, 345.

\bibitem[{}]{Coddens et al. (1999)}[{}]{itapdb:Coddens1999}

{\sc {Coddens},~G., {Lyonnard},~S., {Hennion},~B.,} and {\sc {Calvayrac},~Y.},
 \newblock 1999, {\it Phys.\ Rev.\ Lett.}, {\bf 83}, 3226.

\bibitem[{}]{Edagawa et al. (2004)}[{}]{itapdb:Edagawa2004}

{\sc {Edagawa},~K., {Mandal},~P., {Hosono},~K., {Suzuki},~K.,} and {\sc {Takeuchi},~S.},
 \newblock 2004, {\it Phys.\ Rev.}~B, {\bf 70}, 184202.

\bibitem[{}]{Edagawa et al. (2002)}[{}]{itapdb:Edagawa2002}

{\sc {Edagawa},~K., {Suzuki},~K.,} and {\sc {Takeuchi},~S.},
 \newblock 2002, {\it J.\ All.\ Comp.}, {\bf 342}, 271.

\bibitem[{}]{Engel and Trebin (2005)}[{}]{itapdb:Engel2005}

{\sc {Engel},~M.,} and {\sc {Trebin},~H.-R.},
 \newblock 2005, {\it Phil.\ Mag.}, in press.

\bibitem[{}]{Feuerbacher and Heggen (2005)}[{}]{itapdb:Feuerbacher2005}

{\sc {Feuerbacher},~M.,} and {\sc {Heggen},~M.},
 \newblock 2005, {\it Phil.\ Mag.}, this volume.

\bibitem[{}]{Francoual et al. (2003)}[{}]{itapdb:Francoual2003}

1
2
3 {\sc {Francoual},~S., {Livet},~F., de~{Boissieu},~M., {Yakhou},~F.,
4 {Bley},~F., {Letoublon},~A., {Caudron},~R.,} and {\sc {Gastaldi},~J.},
5 \newblock 2003, {\it Phys.\ Rev.\ Lett.}, {\bf 91}, 225501.
6
7 \bibitem[{{Katz} and {Gratias}(1993)}]{itapdb:Katz1993}
8 {\sc {Katz},~A.,} and {\sc {Gratias},~G.},
9 \newblock 1993, {\it Journ.\ Non-Cryst.\ Solids}, {\bf 153-154}, 187.
10
11 \bibitem[{{Klein} et~al.(2000)}]{itapdb:Klein2000a}
12 {\sc {Klein},~H., {Durand-Charre},~M.,} and {\sc {Audier},~M.},
13 \newblock 2000, {\it J.~All.\ Comp.}, {\bf 296}, 128.
14
15 \bibitem[{{Klein} et~al.(1999)}]{itapdb:Klein1999}
16 {\sc {Klein},~H., {Feuerbacher},~M., {Schall},~P.,} and {\sc {Urban},~K.},
17 \newblock 1999, {\it Phys.\ Rev.\ Lett.}, {\bf 82}, 3468.
18
19 \bibitem[{{Heggen} and {Feuerbacher}(2005)}]{itapdb:Heggen2005}
20 {\sc {Heggen},~M.,} and {\sc {Feuerbacher},~M.},
21 \newblock 2005, {\it Phil.\ Mag.}, this volume.
22
23 \bibitem[{{Mompou} et~al.(2004)}]{itapdb:Mompou2004}
24 {\sc {Mompou},~F., {Caillard},~D.,} and {\sc {Feuerbacher},~M.},
25 \newblock 2004, {\it Phil.\ Mag.}, {\bf 84}, 2777.
26
27 \bibitem[{{Rosenfeld} et~al.(1995)}]{itapdb:Rosenfeld1995a}
28 {\sc {Rosenfeld},~R., {Feuerbacher},~M., {Baufeld},~B., {Bartsch},~M.,
29 {Wollgarten},~M., {Hanke},~G., {Beyss},~M., {Messerschmidt},~U.,} and {\sc
30 {Urban},~K.},
31 \newblock 1995, {\it Phil.\ Mag.\ Lett.}, {\bf 72}, 375.
32
33 \bibitem[{{Steurer}(2004)}]{itapdb:steurer2004}
34 {\sc {Steurer},~W.},
35 \newblock 2004, {\it Z.~Kristallogr.}, {\bf 219}, 391.
36
37 \end{thebibliography}
38
39 \newpage
40 {\large{Figure captions}}
41
42 \begin{enumerate}
43 \item Calculated tilings for various approximants of the AlPdMn i-phase. (a)
44 1.6~nm phases: The tiling of the d-phase is the T\ubingen Triangle Tiling
45 (TTT). (b) 1.2~nm phases: The D' centres lie on a τ^2 inflated
46 TTT. (c) The tiles can be substituted with Penrose rhomb tiles. The
47 substitution is different for the 1.6~nm phases and the 1.2~nm phases.
48 \item Tilings of the ξ'_3 - (left) and the T_3 -phase (right) with
49 $m=4$ metadislocations. $2F_m$ new phason planes are inserted from the
50 left, ending at the triangular shaped dislocation core.
51 \end{enumerate}
52
53 \end{document}