



HAL
open science

Nanostructured silicon and its application to solar cells, position sensors and thin film transistors

Rodrigo Ferrão Paiva Martins, Leandro Raniero, Luis Pereira, Daniel Costa,
Hugo Aguas, Sonia Pereira, Leonardo Silva, Isabel Ferreira, Elvira Fortunato,
Alexandra Goncalves

► **To cite this version:**

Rodrigo Ferrão Paiva Martins, Leandro Raniero, Luis Pereira, Daniel Costa, Hugo Aguas, et al.. Nanostructured silicon and its application to solar cells, position sensors and thin film transistors. Philosophical Magazine, 2009, 89 (28-30), pp.2699-2721. 10.1080/14786430902886910 . hal-00519085

HAL Id: hal-00519085

<https://hal.science/hal-00519085>

Submitted on 18 Sep 2010

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Nanostructured silicon and its application to solar cells, position sensors and thin film transistors

Journal:	<i>Philosophical Magazine & Philosophical Magazine Letters</i>
Manuscript ID:	TPHM-08-Oct-0362.R3
Journal Selection:	Philosophical Magazine
Date Submitted by the Author:	20-Feb-2009
Complete List of Authors:	Martins, Rodrigo; Universidade Nova de Lisboa, Dept. de Ciencia dos Materiais da Faculdade de Ciencias e Tecnologia; Faculty of Science and Technology, Materials Science Department Raniero, Leandro; Universidade do Vale do Paraiba, Instituto de Pesquisa e Desenvolvimento Pereira, Luis; Universidade Nova de Lisboa, Dept. de Ciencia dos Materiais da Faculdade de Ciencias e Tecnologia Costa, Daniel; Universidade Nova de Lisboa, Dept. de Ciencia dos Materiais da Faculdade de Ciencias e Tecnologia Aguas, Hugo; Universidade Nova de Lisboa, Dept. de Ciencia dos Materiais da Faculdade de Ciencias e Tecnologia Pereira, Sonia; Universidade Nova de Lisboa, Dept. de Ciencia dos Materiais da Faculdade de Ciencias e Tecnologia Silva, Leonardo; Universidade Nova de Lisboa, Dept. de Ciencia dos Materiais da Faculdade de Ciencias e Tecnologia Ferreira, Isabel; Universidade Nova de Lisboa, Dept. de Ciencia dos Materiais da Faculdade de Ciencias e Tecnologia Fortunato, Elvira; Universidade Nova de Lisboa, Dept. de Ciencia dos Materiais da Faculdade de Ciencias e Tecnologia Goncalves, Alexandra; Universidade Nova de Lisboa
Keywords:	a-Si:H, image processing, nanostructures, position-sensitive detectors, thin-film solar cells, thin-film transistors
Keywords (user supplied):	a-Si:H, image processing, nanostructures

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60



For Peer Review Only

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Nanostructured silicon and its application to solar cells, position sensors and thin film transistors

R. Martins^{1*}, L. Raniero², L. Pereira¹, D. Costa¹⁺, H. Águas¹, S. Pereira¹, L. Silva¹, A. Gonçalves¹, I. Ferreira¹, E. Fortunato¹

¹*Materials Science Department, CENIMAT/I3N, Faculty of Sciences and Technology of New University of Lisbon and CEMOP/UNINOVA, Campus de Caparica, 2829-516 Caparica, Portugal*

²*Universidade do Vale do Paraíba, Instituto de Pesquisa e Desenvolvimento, Av. Shishima Hifumi, 2911 – Urbanova, São José dos Campos – SP, Brazil*

This paper reports the performances of small area solar cells, 128 linear integrated position sensitive detector arrays and thin film transistors based on nanostructured silicon thin films produced by plasma enhanced chemical vapour deposition technique, close to the onset of dusty plasma conditions, within the transition region from amorphous to microcrystalline. The small area solar cells produced in a modified single chamber reactor exhibited very good electrical characteristics, with a conversion efficiency exceeding 9 %. The 128 integrated position sensitive detector arrays, based on similar pin structure, allow real time 3D object imaging with a resolution higher than 90 lp/mm. The thin film transistors produced exhibited field effect mobility of $2.47 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$, threshold voltage of 2 V, on/off ratio larger than 10^7 and sub-threshold slopes of 0.32 V/decade, which are amongst the best results reported for this type of device.

Keywords: nanostructured silicon; thin film devices; position sensitive detectors, TFTs, solar cells

⁺ on leave to Qimonda, Estrada Nacional 13 km 19, 4480-054 Vila do Conde, Mindelo, Portugal

1. Introduction

Amorphous silicon (a-Si:H) has been studied for many years [1-3] with a particular emphasis on optoelectronic devices since the demonstration of doping effect by Spear [4]. This material has been intensively studied worldwide involving thousands of researchers and the work of Spear [5, 6] and LeComber [7-9], among others, have been central references. To these studies we have to add the earlier work of Madan et al. [10] in determining the density of localized states that not only supported the development of high grade electronic quality undoped amorphous silicon for device applications, but also was the precursor in the use of amorphous silicon in field effect transistors [11]. Since then the main bottleneck has been the inherent light degradation of a-Si:H [12] and the low carrier mobility which prevents even larger application potential of the material. To overcome the carrier mobility limitation, several authors proposed the production of new silicon alloys [13] or structured ordered thin silicon such as microcrystalline [14-16], polymorphous [17] or protocrystalline [18] silicon. As far as devices are concerned, the main driving force has been its use in solar cells [19], field effect transistors/thin film transistors [20] and sensors [21-25]. Other possible applications have also been tried such as switching memories [26], tunnelling based devices [27], large area position sensitive detectors, (psd) [28, 29] or in biosensors [30, 31].

It seems that the degradation is due to the metastability in a-Si:H and closely related to the amorphous network nature and the vast amount of hydrogen atoms within the films. Therefore in order to improve stability and electronic performance, the microstructure must be improved. To reach this goal we produced hydrogenated diphasic nanostructured silicon thin films close to the onset of dusty plasma conditions, within the amorphous to microcrystalline transition region, using high hydrogen dilution conditions [32-36].

In honour of Professor Walter Spear and his strong contribution to the field of amorphous silicon, related alloys and their integration into devices, we present here the results concerning the process conditions used to produce nanostructured hydrogenated silicon (ns-Si:H) and its application in solar cells, psd integrated arrays [37, 38] and TFT's. The psd 128 integrated array is presented for the first time and fully integrated into a linear camera that allows for real time 3D inspection imaging. Concerning the TFT, the aim is to show that a high performance device can be produced with the material developed as well as to prove that other materials, other than silicon dioxide or silicon nitride, [39] can be successfully used as the dielectrics.

2. Experimental details

2.1. Material deposition

The nanostructured thin films were deposited by plasma enhanced chemical vapour deposition (PECVD) at 27.12 MHz, using a single chamber as described elsewhere [34, 40]. The main features of these types of films when compared to the amorphous silicon are the improvement of the short range order and a particular signature given by the hydrogen exodiffusion data (there is a characteristic peak, absent in the amorphous silicon, shifted to high temperatures, when compared to the microcrystalline silicon). Also noticeable is the absence of the usual high hydrogen content measured by infrared spectroscopy that is considered one of the polymorphous finger prints, [14] and the absence of a distinct phase with a low hydrogen concentration occurring during the crystal growth, which evolves into a microcrystalline form (the so-called protocrystalline [15]) [41].

The deposition pressure (p) and the substrate temperature (T_s) were fixed at 187 Pa and 473 K, respectively. The influence of silane concentration [$d_r = \text{SiH}_4 / (\text{SiH}_4 + \text{H}_2)$] and the role of power density (P_d) on the films' properties were studied on the range from 1 to 9 %, and from 63 to 383 mW/cm², respectively. The d_r was varied by increasing the silane flow in the mixture, from 1 to 9 sccm, keeping the hydrogen flow constant (100 sccm).

The films deposited were studied by Micro-Raman Spectroscopy and exodiffusion measurements. The exodiffusion data allow the determination of the exodiffusion hydrogen activation energy for the set of films produced, which was deduced from the relation between the heating rate (ϕ) and the peak temperature (T_m) given by equation 1 [42].

$$\frac{E_a \phi}{RT^2} = A e^{\left(\frac{-E_a}{RT}\right)} \quad (1)$$

where A is the reaction constant, R is the gas constant (8.31 J/mol.K), T is the absolute temperature and E_a is the activation energy for the evolution process.

1
2
3 Taking logarithms on both sides of equation 1 and differentiating it with respect to $1/T_m$
4
5 yields [43]:
6

$$\ln\left(\frac{\phi}{T_m^2}\right) / \left(\frac{1}{T_m}\right) = \frac{E_a}{R} \quad (2)$$

7
8
9
10
11

12 From the slope of a $\ln(\phi/T_m^2)$ versus $(1/T_m)$ plot the E_a was calculated using the Kissinger's
13 method [44] which has been used to determine the activation energy of solid state reactions,
14 through the method of differential thermal analysis. In this method the dominant factor
15 controlling the shape and position of the differential thermal analysis peak is the nature of the
16 reaction itself. The heating rate was varied between 3 to 10 K/minutes.
17
18
19
20
21
22
23

24 **2.2. Solar cells deposition**

25
26
27

28 The solar cell with a p-doped layer/buffer1/buffer2/i-n-Si:H layer/ n-doped/Ag/Al
29 structure was deposited on Gallium Zinc Oxide (GZO) coated glass substrate, as described
30 elsewhere [45], using the material deposition conditions defined in section 2.1. The two buffer
31 layers are used to adjust the mismatch in the optical band gap between the p- (1.94 eV) and i-
32 (1.82 eV) layers. The band gap of buffer₁ is 1.88 eV and that of buffer₂ is 1.84 eV.
33 Additionally, the buffer layers are efficient in controlling the diffusion between the dopants of
34 the p- and i- layers [46-48]. The back contact consists of a thin Ag layer (≈ 30 nm) used to
35 improve the light reflectance, followed by an Al layer (≈ 170 nm) with an electrode area of
36 0.07 cm^2 [49]. Table 1 summarizes the characteristics of the different layers as well as the gas
37 mixtures used. the silicon structure was removed by dry etching technique in order to avoid
38 interference of the current collected in the vicinity surrounding the contact [50]. The study of
39 these devices also served to establish the optimised process conditions for producing the
40 integrated psd arrays. The solar cell performance was measured using a sun simulator under
41 AM1.5 illumination conditions.
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

2.3. *Linear Integrated psd Arrays Fabrication and Characterization*

The linear integrated array consisted of 128 psd's configured as a nip structure processed using similar conditions to the ones described for solar cells, with the exception that the intrinsic layer has a thickness above $0.8\mu\text{m}$. Details concerning the fabrication steps of the psd arrays are given in previous papers [51]. The device linearity versus incident light frequency measurements were taken in the photoconductive mode [37, 51, 52], where the back metal contact was grounded or reverse biased at -1 V and the photocurrents detected at the pad electrodes located on the device edges (see Figure 1). The devices are mounted over a collecting Printed Circuit Board (PCB) unit that contains the controller unit, the analogical/digital (A/D) converter and the MX4 microprocessors, whose schematic is depicted in Figure 2. The functional characteristics of this 128 psd integrated array are depicted in Table 2. The PCB board is connected to the PC via an acquisition data board from National Instruments (NI 6031E). The detection system used to obtain a 3D image directly out of the integrated psd array is depicted in Figure 2, and the camera performance is shown in Table 3. The light source is a diode laser (670 nm , 5 mW), that generates a line focused by a lens towards the surface to be inspected. The linear movement of the device was achieved using an automated control table (Parker-Hannifin M106061S 5M) with a spatial resolution better than $5\text{ }\mu\text{m/turn}$. All the experimental data were gathered using custom-developed software for data acquisition and control.

The main properties of the layers that constitute the devices such as thickness, conductivity and optical gap are the same used to process the solar cells described in section 2.2 and referred in Table 1.

2.4. *Thin Film Transistor Fabrication and Characterization*

For thin film transistors processing the substrate is located in the dark region of the plasma, underneath a grounded metal grid. By not exposing the growth surface directly to the plasma we avoided the high ion bombardment at the silicon growth surface leading to a less defective surface and highly compact films.

The TFT's were produced using different dielectric layers in a bottom gate configuration, as depicted in Figure 3. The materials used as dielectric were a multilayer of aluminium oxide and titanium oxide, known as ATO; silicon oxide (SiO_2) and hafnium oxide (HfO_2) [53]. In the first case, the dielectric was deposited by Atomic Layer deposition (ALD) over indium tin oxide (ITO) that acts as gate electrode. The substrate (glass)/ITO/ATO stack was supplied by Plannar Systems Inc. The SiO_2 was obtained by thermal oxidation of highly doped p-type silicon that was metalized on the back surface to form the gate electrode. The HfO_2 was deposited by r.f. sputtering over the gate electrode (sputtered indium zinc oxide - IZO). Both layers (dielectric and gate electrode) were patterned by lift-off lithography.

The deposition of the ns-Si:H channel layer with 120 nm thickness was done by PECVD at 200°C, with a power density of 128 mWcm^{-2} , at 27.12 MHz, following similar procedures as the ones described in section 2.1, with an aim to obtain nanostructured silicon films (ns-Si:H). The deposition pressure selected was 186 Pa and the total gas flow 105 sccm with $d_r \cong 5\%$. The source and drain n-type a-Si:H was deposited right after ns-Si:H, without breaking vacuum, also at 200°C. In this case the power density was 35 mWcm^{-2} , using the same 27.12 MHz generator, while the pressure and gas flow ($\text{PH}_3/\text{SiH}_4/\text{H}_2/\text{He}$ mixture) were 86 Pa (0.65 torr) and 10 sccm, respectively. The growth rate changes from about 10-12 nm/min to 6-8 nm/min for films grown with or without the grid, respectively. An Al layer 200 nm thick was evaporated on top of the n-type silicon. The source and drain electrodes were then patterned by photolithography and wet etching using a $\text{H}_2\text{PO}_4:\text{HNO}_3:\text{H}_2\text{O}$ solution.

1
2
3 This metal layer serves as a mask for the n-type silicon etching by Reactive Ion Etching
4 (RIE). The etching time was accurately monitored, to allow for the removal of just the doped
5 layer deposited over the channel layer. The devices were terminated by patterning the channel
6 layer also by photolithography and RIE. In order to enhance the device performance
7 annealing at 200°C in a forming gas (95%N₂-5%H₂) atmosphere was performed. The
8 electrical characterization of the TFT was performed using an Agilent 4155C semiconductor
9 analyzer connected to a Microprober Cascade M150, installed inside a dark box.
10
11
12
13
14
15
16
17
18
19
20
21
22

23 **3. Results**

24 **3.1. Processed materials**

25
26
27
28
29 Figure 4 shows typical micro-Raman results of the nanostructured films produced
30 (dotted line) and reference data spectra concerning amorphous (dashed line) and
31 microcrystalline (solid line) silicon thin films. The peak shift observed (from ~480 cm⁻¹ to
32 ~485 cm⁻¹) is also seen in polymorphous films and it is attributed to the improvement of the
33 structural order at the nanoscale level [32, 54].
34
35
36
37
38
39
40

41 The hydrogen exodiffusion spectra as a function of temperature are shown in Figure 5.
42 Figure 6 summarizes all the plasma conditions that lead to the production of materials with
43 different type of structures (from amorphous to microcrystalline) as a function of P_d and d_r
44 used. There we can see the different process conditions that lead to the production of silicon
45 thin films where the amorphous or microcrystalline phases clearly dominate. In-between we
46 can see the transition region, where both phases may exist: close to the microcrystalline phase
47 the predominant structure is dominated by the existence of nanocrystals while close to the
48 amorphous region we may still have a dominant amorphous phase but with a highly improved
49 short range order.
50
51
52
53
54
55
56
57
58
59
60

1
2
3 Figure 7 shows the change in the low temperature (LT) and high temperature (HT)
4 peaks position as a function of P_d , for films produced at high deposition rate, using $d_r = 5\%$.
5
6 The films deposited at the lowest P_d are amorphous, while the LT exodiffusion peak is related
7
8 to the weak hydrogen silicon bonds. Thus, for $94 \text{ mW/cm}^2 < P_d < 128 \text{ mW/cm}^2$, the films are
9
10 produced in the so-called transition region and the LT peak increases, when compared to the
11
12 one due to amorphous films. For films with $P_d > 160 \text{ mW/cm}^2$ the crystalline fraction of the
13
14 films increases and the hydrogen situated around the grains can diffuse easier through the
15
16 network and the LT peak shifts towards 643K.
17
18
19
20
21
22
23
24

25 **3.2. Device results**

26 **3.2.1. Solar cells**

27
28
29
30
31
32 Figure 8a) shows the cross section of the solar cell. The image reveals a highly
33
34 compact structure, where we note the typical dense columnar structure of the polycrystalline
35
36 GZO, exhibiting a bulk resistivity of $2.5 \times 10^{-4} \Omega\text{-cm}$, a mobility close to $20 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$ and a
37
38 transmittance in the visible range above 82% for a film thickness of about $1.35 \mu\text{m}$ [55-57].
39
40 Besides that the GZO films clearly sustain the plasma process as observed when analyzing
41
42 different types of TCO after sustain an intense hydrogen plasma by 600 s [58], not suffering
43
44 any chemical or physical degradation. Near the glass/GZO interface small grains are
45
46 observed. On the other hand a highly compact structure near the surface makes it impossible
47
48 to distinguish between grain boundaries, defects or voids.
49
50
51
52

53
54 The image also reveals a well compacted and dense pin structure, where no large
55
56 crystallites or grains can be seen. That is, we are in the presence of an almost amorphous film
57
58 where the short range order has been improved, in spite of the hydrogen content of these films
59
60 [35].

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Figures 8b) and 8c) show the J-V characteristics and quantum efficiency curves for the produced small area solar cells.

3.2.2. *Integrated psd arrays*

In Table 3 we present the characteristics of the 128 integrated arrays produced. Figure 9 shows the results of the spatial resolution determined in 1D psd element of the array, using spatial steps down to a minimum of 0.25 μm allowed by the measuring system, and a focus light of 50 mW/cm^2 . As observed both measurements are linear but the proximity of the points in the 0.25 μm measurement causes the current to oscillate in a way that one value of current can correspond to two or three positions, which would lead to an inaccuracy in its position. That is, the random distribution of currents measured to determine a clear position is out of the admissible error window. In spite of this, a still linear behaviour can be foreseen. This means that the minimum resolution of the sensor is higher than 0.25 μm . With the 1 μm step measurements the case of a current value corresponding to two or more positions does not occur, so with 1 μm step it is already possible to determine a position with an accuracy of $\pm 0.5 \mu\text{m}$.

3.2.3. *Thin film transistor*

Figure 10a) shows the transfer characteristics and the transconductance (g_m) variation with the gate voltage (V_{GS}), for the set of TFTs analysed using different dielectrics. The typical electrical parameters extracted from the transfer characteristics such as the field effect mobility (μ_{FE}), threshold voltage (V_T), on/off ratio (I_{on}/I_{off}) and sub-threshold slope (S) are shown in Table 4. In Figure 10b) the transfer characteristics of the TFT produced using different channel dimensions, on linear ($V_{DS}=1\text{V}$) and saturation regimes ($V_{DS}=10\text{V}$), for ns-Si:H TFT with different channel dimensions integrating SiO_2 as dielectric are shown. In

9/25

1
2
3 Figure 10c the transfer characteristics of a TFT produced using the protection grid with
4 optimized holes dimension (1.5 times bigger in diameter) is presented. The electrical
5 parameters extracted from these data are shown in Table 5.
6
7
8
9

10 11 12 13 14 **4. Discussion**

15 16 **4.1. *Materials properties***

17
18
19 The spectra in Figure 4 show the three main types of materials produced, which are: 1)
20 amorphous films, represented by a single Gaussian peak centred around 480 cm^{-1} [59]; 2) the
21 microcrystalline films, with a band close to the sharp peak around 516 cm^{-1} ; 3) the
22 nanostructured films, represented by an improved short range order, where some nanocrystals
23 exist ($<2\%$). This is conjectured by a slight shift of the amorphous peak towards higher
24 wavenumbers together with a slight narrowing of the full width at half maximum (FWHM).
25 This shift towards higher wavenumbers can be attributed to the presence of nanocrystals
26 randomly distributed in the the film or to the improvement of the short range order. The
27 presence of such nanocrystals (of small size, $< 10\text{ nm}$) and of short range order clusters can
28 lead to an internal film stress that are responsible for the shift observed [59].
29
30
31
32
33
34
35
36
37
38
39
40
41
42

43 The exodiffusion data are shown in Figure 5 and together with the illustrations helps
44 to understand the characteristics of the structure of the materials developed. The films with
45 different structures have different ways to release the bonded hydrogen, as a function of the
46 sample's temperature. The first highest peak (at low temperature - LT) corresponds to
47 hydrogen exodiffusion from microcrystalline silicon, due to loosely bonded hydrogen at the
48 grain boundaries, while the HT peak of the same spectrum corresponds to hydrogen tightly
49 bonded to silicon in the remaining amorphous phase.
50
51
52
53
54
55
56
57
58
59
60

1
2
3 With respect to the amorphous silicon film, in the exodiffusion spectrum (dash line)
4 the LT peak represents the weak $\text{SiH}_2/\text{SiH}_3$ bonds and cluster adsorbed by physisorption
5 originated from van der Waals interaction. The illustration (b) depicted in Figure 5 shows a
6 nanostructured film, which shares some similarity with a microcrystalline structure since we
7 also have the presence of some grain boundaries, but now with a large fraction of amorphous
8 tissue. This explanation is in agreement with the collected exodiffusion spectrum where a
9 third spectrum corresponding to films produced in the so-called transition region, where the
10 present films have been deposited, is shown. In this spectrum the LT peak is shifted towards
11 703 K (about 60 K above the previous LT peak). Its position peak can be explained by the
12 presence of a mixed phase material (disorder/short range order or disorder/nano-order), where
13 tightly bonded hydrogen prevalent in the amorphous tissue with a combination of hydrogen in
14 possible cavities or in the boundaries of nano-grains. These data, together with the role of
15 hydrogen dilution and P_d used, leads to the schematic shown in Figure 6, where a small
16 “window” corresponding to films deposited on the transition region is defined. The transition
17 region where nanostructured films can be processed depends on the reactor configuration and
18 temperature uniformity on the deposition chamber [32, 60, 61].

19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41 Indeed the interaction between atomic hydrogen and the surface during the deposition
42 process markedly influences the type of structured film obtained [62]. As observed in
43 Figure 7, the hydrogen evolution in films produced in the transition region reveals that they
44 have a compositional structure different from that of conventional amorphous silicon. In order
45 to compare the films' properties, the exodiffusion hydrogen activation energy was calculated
46 using the Kissinger's method [44]. The values recorded for the nanostructured films at LT and
47 HT peaks are shown in Figure 11, and the data fitted by equation 2. The E_a data reported in
48 the literature for amorphous silicon for the LT and HT peaks are 79 KJ/mol and 112 KJ/mol,
49 respectively [42]. On the other hand, the E_a data obtained for the nanostructured films for the
50
51
52
53
54
55
56
57
58
59
60

1
2
3 LT and HT peaks are respectively 87 KJ/mol and 135 KJ/mol. The increase of E_a regarding
4
5 the HT peak is related with hydrogen being more tightly bonded in the amorphous phase,
6
7 while the higher values for the LT peak can be attributed to the formation of hydrogen bonds
8
9 in nanocavities or in the boundaries of nano-grains. This material, fabricated in the transition
10
11 region, was used to fabricate devices such as solar cells, position sensitive detectors and thin
12
13 film transistors, whose electronic performances are discussed below.
14
15
16
17
18
19
20

21 **4.2. Solar cells**

22
23 The analysis of the plots shown in Figure 8 for single junction solar cells based on ns-
24
25 Si:H films leads to a fill factor of 0.67, an open circuit voltage of 0.94 V and a short circuit
26
27 current density of 14.48 mA/cm^2 , leading to a conversion efficiency of 9.12 %.
28
29
30

31 The high current density and good value obtained for the quantum efficiency are
32
33 mainly attributed to the quality of the i-layer and to the p/i interface that does not annihilate
34
35 the photocarriers generated, and the use of GZO as the front contact contributes since it is not
36
37 degraded by the hydrogen plasma during the deposition of the p-layer [45-47]. This is
38
39 probably due to the stability of the GZO leading to improved transmittance at the blue region
40
41 of the spectrum. The high value of open circuit voltage is related to the wide band gap and
42
43 high work function of GZO (respectively above 3.4 eV and 4.95 V), which leads to an
44
45 enhancement of the band offsets between the p-type silicon front layer and the transparent
46
47 conductive oxide layer used [63]. This analysis is supported by data achieved on similar solar
48
49 cells where the only change in fabrication was to use the conventional amorphous i-layer,
50
51 keeping all other constituent layers the same. The data achieved under these conditions lead to
52
53 short circuit current, fill factor and open circuit voltage of 13 mAcm^{-2} , 0.62 and 0.92V
54
55 respectively, leading to overall device efficiency of 7.4%. After continuous AM1.5
56
57
58
59
60

illumination for 250 h, we notice that the overall efficiency of the solar cells stabilizes to a value around 8.50%, showing that these devices are more stable than a-Si:H based solar cells where a strong device degradation, sometimes exceeding 20% has been reported [46]. These data cannot be compared with industry data where the devices are differently processed, as are the recent reported data from MVSsystems and United Solar for instance [64-69]. The aim is to prove the consistency of the laboratory results [63] and the integration of these nanostructured silicon thin films in device structure such as solar cells, thin film position sensitive detectors and thin film transistors.

4.3. Integrated psd arrays

4.3.1. Working principles

The operation principle of the psd array is that an image line projected in the array induces photocurrents (I_{ph1} and I_{ph2}) or lateral photo voltages ($\Delta V=V_1-V_2$) in the illuminated elements (see Figure 12). Then all elements are scanned to determine the position of the image line. In this case the angle of incidence that the laser line makes with the surface to be inspected should be such that allows its detection along the length of the detector. That is, the maximum active length d_d of each element of the array has to be such that:

$$d_0(max) \geq \frac{d_d(max)}{\cos \phi}, \quad (3)$$

where d_0 is the distance between the sensor and the surface to be scanned [70, 71]. Each element ΔI_{ph} has an uncertainty related to the noise (n) and so, the measure position is given by:

$$P(y_n) = \frac{(I_{ph1} \pm n_1) - (I_{ph2} \pm n_2)}{(I_{ph1} \pm n_1) + (I_{ph2} \pm n_2)} \cdot \frac{L}{2} \Rightarrow P_{max}(y_n) = \frac{I_{ph1} - I_{ph2}}{I_{ph1} + I_{ph2} - 2n} \cdot \frac{L}{2}, \text{ for } n_1=n_2=n \quad (4)$$

where n_1 and n_2 are the absolute noise detected at each of the element terminals and L is the length of each line. Thus, the position of an image line projected in the plane z - y is determined by $P(y_n)$ obtained by the 128 stripes and related to the currents detected by the MX8 connected to the terminals of integrated arrays.

The detection threshold limit will depend on the signal to noise ratio (S/N), which is given by $S/N = \frac{I_{ph1} + I_{ph2}}{2n}$. Thus, the positional resolution (dP) depends on the active length of each sensing element and on (S/N): $dP \approx \frac{L}{2S/N}$.

Once established the proper S/N ratio, the performance of the 128 psd arrays is mainly dependent on the maximum distance at which a light spot from each of the collecting electrodes can be detected with a linear correlation between the spatial position and the lateral photocurrent measured [70].

As we aim to use these devices to supply planar information about 3-D objects (images) we should also define the Modulation Transfer Function (MTF) as the appropriate image quality criteria in the frequency spatial domain (specifying resolution and perceived image sharpness) [72]. That is, the contrast at a given spatial frequency relative to low frequencies.

In this case, the spatial frequency (ν) is typically measured in cycles or line pairs per millimetre (lp/mm). Therefore, high spatial frequencies correspond to fine image details.

In our case, MTF will correspond to how well the input signal is preserved after being imaged. To do so we determine the Fast Fourier Transform of the signal and convert it into the frequency domain to define the pattern conditions that lead to proper spatial signal discrimination. That is:

$$MTF(\nu) \approx \frac{I_{max}(\nu) - I_{min}(\nu)}{I_{max}(\nu) + I_{min}(\nu)} \quad (5)$$

where I_{max} and I_{min} correspond to maximum and minimum currents discriminated between two consecutive spatial points. Thus, proper image plane resolution will correspond to the inverse of ν for which MTF has some meaning concerning image preservation and metric details. Finally, we have to consider the device nonlinearity of each strip (position detection error) (δ):

$$\delta = 2\sigma/F \quad (6)$$

where σ is the *rms* (root mean square) deviation from the regression line data and F is the full scale measured.

4.3.2. Integrated 128 psd arrays performances

The process conditions selected for fabricating the integrated psd arrays were the same used to fabricate the solar cells. Thus, once established the proper sensor geometry and before performing any measurement the conditions for light illumination of the array were defined. The detailed information concerning the detection platform and the integrated array is given in Tables 2 and 3.

The minimum light power allowable Pl , that permits a good linear correlation with a spatial detection error below $\pm 4\%$, was approximately 50 nW/line for the integrated devices under analysis.

To determine the image plane resolution the Modulation Transfer Function (MTF) required to preserve proper image detail and information must be known. Following equation (5) this means that $MTF=0$ when $\nu=2000$ lp/mm. Taking into account that the array has 128 elements we reach the set of data depicted in Figure 13. Considering that for a good image plane resolution $MTF \leq 10\%$, we obtain the maximum ν at about 90 lp/mm, from which we estimate that $I_{max}/I_{min} \geq 1.2$, to get a sharp image. Besides that, taking into account the laser

1
2
3 visible line used (red) the best performance is obtained for highly reflected surfaces for such
4
5 colour, as it is the case of white surfaces.
6
7

8 Figure 14 shows the object scanned and the image collected using the laser triangulation
9
10 principle and the detection system that integrates the sensor described above, in real time,
11
12 without any type of data treatment. It should be noted that a very good image is directly
13
14 collected, which allows a fast 3D scan inspection or the reconstruction of surfaces, such as
15
16 moulding features as the ones used to rebuild bones or teeth in the life sciences area.
17
18

21 **4.4. Thin film transistors**

22
23
24
25 The performances of the ns-Si:H TFTs analyzed using different dielectrics and channel
26
27 lengths are summarized in Tables 4 and 5 and Figure 10. Overall, we notice a significant
28
29 progress since the first device reported by LeComber et al [11] and the present values are
30
31 amongst the highest found in the literature for a-Si:H [73-79] or nanostructured silicon TFTs
32
33 [80-82]. The improvement observed on the TFTs performance is mainly related to two
34
35 factors: lower growth rate used and the reduced hydrogen bombardment at the growing
36
37 surface, which reduce defects.
38
39

40
41 For devices produced using ATO as the dielectric, the maximum on/off ratio was
42
43 estimated since the transfer curve in the linear regime is not totally defined for source and
44
45 drain current (I_{DS}) below 10^{-12} A. This effect is now under investigation and seems to be
46
47 induced by ATO and does not correspond to measuring limitations. Thus, we can only say
48
49 that the on/off ratio is higher than 10^7 . Also the sub-threshold slope calculation is affected by
50
51 the incomplete definition of the I_{DS} current below 10^{-12} A.
52
53

54
55 The data of ns-Si:H TFTs using thermally oxidized silicon and hafnium oxide as dielectric
56
57 are also depicted in Figure 10a). The electrical characteristics of the devices produced on SiO₂
58
59 (see **Table 4**) are even better when compared with those using ATO. The field effect mobility
60

1
2
3 is now $1.24 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$, while the I_{DS} is well defined down to 10^{-14} A , closer to the
4 semiconductor analyser measuring limit. So we can clearly state that the on/off ratio is well
5 above 10^7 , which confirms that the dark conductivity of ns-Si:H layer is low, allowing off
6 currents on TFTs below 10fA. The threshold voltage is slightly higher when compared with
7 ATO devices. This can be explained by the lower capacitance of SiO_2 , which is $34 \text{ nF} \cdot \text{cm}^{-2}$,
8 on a 100 nm thick layer, when compared to the $64 \text{ nF} \cdot \text{cm}^{-2}$ of ATO. Besides this we must also
9 take into account that the gate electrode is different, which contributes to changes on the V_T
10 value.
11
12

13 TFTs integrating a high k dielectric such as HfO_2 were also produced (see Figure 10a).
14 For a thickness of 300 nm we found a capacitance of $50 \text{ nF} \cdot \text{cm}^{-2}$, corresponding to a dielectric
15 constant around 17. The electrical performance exhibited by these devices is not so
16 impressive, which is attributed to the high roughness of the dielectric surface. Despite being
17 deposited at room temperature, sputtered HfO_2 normally presents a microcrystalline structure
18 [53] which leads to a rough surface morphology in opposition to the smooth surfaces of
19 amorphous ATO and SiO_2 . This contributes to the creation of defects on the
20 dielectric/semiconductor interface side of the bottom gate of the TFTs, affecting g_m and so μ_{FE}
21 and V_T . Also the density of fixed charge in a 300nm HfO_2 layer, which is normally positive
22 and around 10^{12} cm^{-2} for sputtered films deposited at room temperature, is pushing the V_T
23 towards high values (5.19V).
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47

48 Since the use of SiO_2 leads to better electrical performance on ns-Si:H based TFTs, this
49 dielectric was employed to monitor the effect of the channel length. A device with a W/L of
50 $50 \mu\text{m}/50 \mu\text{m}$ is compared with the one already presented in Figure 10a), where the channel
51 dimensions, W/L are $15 \mu\text{m}/15 \mu\text{m}$. Transfer characteristics on linear and saturation regimes as
52 well as the extracted electrical parameters exhibited by these devices are respectively depicted
53 in Figure 10b) and summarized in Table 4. The data obtained show that g_m increases about
54
55
56
57
58
59
60

1
2
3 50%, which corresponds to $\mu_{FE} = 1.84 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$. However, V_T and S for long channel TFTs
4
5 are respectively 20% and 10 % higher than the values obtained in short channel TFTs. This
6
7 behaviour is attributed to the effect of the contact resistance (R_C) at source and drain regions
8
9 that is known to negatively affect the device's mobility, since the effective source to drain
10
11 voltage is given by $V_{DS} - R_C I_{DS}$ [83]. Besides affecting the mobility, the contact resistance
12
13 induces an error in extracting the device power parameter and V_T by the amount of $R_C I_{DS}/2$.
14
15 This limitation is more pronounced on short channel devices, since I_{DS} is proportional to
16
17 V_{DS}/L . The highest field effect mobility value ($2.47 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$) was obtained for devices
18
19 where the active layer was produced using an optimized grid with larger holes (named 50/50
20
21 OG - fig. 10c). In this case their diameter is 1.5 times larger than the ones used for fabricating
22
23 the other devices, allowing a better balance of the hydrogen bombardment effect on the films
24
25 properties. This is also reflected on the other electrical parameters determined from the
26
27 transfer curve (see Table 5).
28
29
30
31
32
33
34
35
36
37

38 5. Conclusions

39
40 In this work we have focussed on the deposition of nanostructured silicon (ns-Si:H) by
41
42 PECVD in the so-called transition region and have shown improved properties, in comparison
43
44 with amorphous silicon, when included in diverse applications. The hydrogen exodiffusion
45
46 evolution observed on samples produced in this transition region shows two peaks, one at low
47
48 temperature (698K) and other at high temperature (840K), associated to E_a of 87 KJ/mol and
49
50 135 KJ/mol, which are completely different from the ones observed in either amorphous or
51
52 conventional microcrystalline thin films. The micro-Raman spectroscopy data show that in
53
54 the transition region the curves shift slightly towards higher wavenumber and becomes
55
56 narrow, which could be explained by the incorporation of nanocrystallites or the existence of
57
58 nanostructured aggregates in the film. The solar cells produced in a single chamber system
59
60

1
2
3 show good quantum efficiency, current density = 14.48 mA/cm^2 , short circuit voltage = 0.94
4
5 V, and fill factor = 0.67, which corresponds to an efficiency of 9.12%, under AM1.5
6
7 conditions.
8
9

10 We have also fabricated 128psd integrated array which is able to satisfy the
11 requirements for 3-D image processing, with a 7 bit lateral digital resolution, speed rates up to
12
13 10000 frames per second, with a detection error below 5%; an image deep resolution of about
14
15 $2.5\text{-}0.2 \mu\text{m}$; a horizontal resolution ranging from $50\text{-}10 \mu\text{m}$; a linearity better than 99.9%, and
16
17 a frequency response better than 500kHz. That is, the integrated array can process frame
18
19 image in real time and fast enough to allow image inspection in a continuous manner.
20
21
22
23

24 The ns-Si:H TFT produced using a grid to control the ion bombardment during the
25 growth process lead to devices with improved μ_{FE} . Among the different types of dielectric
26
27 used it can be seen that TFTs based on SiO_2 exhibit the best μ_{FE} ($1.2 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$), with on/off
28
29 ratio higher than 10^7 and V_T close to 2 V. It was also verified that these TFTs suffer from non
30
31 negligible influence of source and drain contact resistance. This was verified on devices with
32
33 longer channel, where μ_{FE} is $\sim 1.84 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$. The optimization of the grid holes dimension
34
35 allowed the improvement of this value to $2.47 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$. Another remarkable result concerns
36
37 the use of other dielectric materials other than the conventional silicon oxide, silicon nitride or
38
39 silicon oxynitride based ones. These are the so-called high k dielectric films, ATO and hafnia,
40
41 where the results achieved indicate a clear window for further improvement on the TFTs
42
43 performance.
44
45
46
47
48
49
50
51
52
53

54 **Acknowledgements**

55
56 The first author would like to thank the Dundee group and to pay tribute to Professor Walter
57
58 Spear who introduced us to the fantastic world of applied disordered semiconductor
59
60 technologies. The contribution for this special issue of the Philosophy Magazine is only

19/25

possible due to the legacy left by Professor W. Spear, in the field of Applied Solid State Physics especially undoped and doped amorphous silicon/germanium and their alloys that significantly contributed to the development of optoelectronic and electronic devices. The authors would also like to thank the financial support given by “Fundação para a Ciência e a Tecnologia” through pluriannual contract with CENIMAT, and projects PTDC/Fis/24274/2006, PTDC/EEA-ELC/74236/2006 and Qren Solar tiles.

References

- [1] N. F. Mott, *Advances in Physics* 16 (1967), p. 49.
- [2] N. F. Mott, *Philosophical Magazine* 19 (1969), p. 835.
- [3] M. H. Cohen, Fritzsche, H. and Ovshinsky, Sr, *Physical Review Letters* 22 (1969), p. 1065.
- [4] W. E. Spear and P. G. LeComber, *Solid State Communications* 17 (1975), p. 1193.
- [5] W. E. Spear and P. G. LeComber, *Philosophical Magazine* 33 (1976), p. 935.
- [6] D. A. Anderson and W. E. Spear, *Philosophical Magazine* 35 (1977), p. 1.
- [7] P. G. LeComber, W. E. Spear and D. Allan, *Journal of Non-Crystalline Solids* 32 (1979), p. 1.
- [8] P. G. LeComber, D. I. Jones and W. E. Spear, *Philosophical Magazine* 35 (1977), p. 1173.
- [9] P. G. LeComber and W. E. Spear, *Physical Review Letters* 25 (1970), p. 509.
- [10] A. Madan, P. G. LeComber and W. E. Spear, *Journal of Non-Crystalline Solids* 20 (1976), p. 239.
- [11] P. G. LeComber, W. E. Spear and A. Ghaith, *Electronics Letters* 15 (1979), p. 179.
- [12] D. L. Staebler and C. R. Wronski, *Journal of Applied Physics* 51 (1980), p. 3262.
- [13] S. R. Ovshinsky and A. Madan, *Nature* 276 (1978), p. 482.
- [14] W. E. Spear, G. Willeke, P. G. LeComber and A. G. Fitzgerald, *Journal De Physique* 42 (1981), p. 257.
- [15] Y. Nagata, A. Kunioka and S. Yamazaki, *Applied Physics Letters* 38 (1981), p. 142.
- [16] H. Richter, Z. P. Wang and L. Ley, *Solid State Communications* 39 (1981), p. 625.
- [17] P. R. I. Cabarrocas, S. Hamma, S. N. Sharma, G. Viera, E. Bertran and J. Costa, *Journal of Non-Crystalline Solids* 230 (1998), p. 871.
- [18] J. M. Pearce, R. J. Koval, A. S. Ferlauto, R. W. Collins, C. R. Wronski, J. Yang and S. Guha, *Applied Physics Letters* 77 (2000), p. 3093.
- [19] D. E. Carlson and C. R. Wronski, *Applied Physics Letters* 28 (1976), p. 671.
- [20] P. G. LeComber and W. E. Spear, *Semiconductors and Semimetals* 21 (1984), p. 89.
- [21] L. E. Antonuk, J. Yorkston, J. Boudry, M. J. Longo, J. Jimenez and R. A. Street, *Ieee Transactions on Nuclear Science* 37 (1990), p. 165.
- [22] H. Kakinuma, M. Sakamoto, Y. Kasuya and H. Sawai, *Ieee Transactions on Electron Devices* 37 (1990), p. 128.
- [23] J. Wind, G. Krotz, R. Schmiedgen, W. Legner, V. Hechtenberg and G. Muller, *Sensors and Actuators a-Physical* 36 (1993), p. 187.
- [24] R. M. Ambrosi, G. W. Fraser, B. Feller, R. Street, J. I. W. Watterson, P. White and G. Downing, *Nuclear Instruments & Methods in Physics Research Section a-Accelerators Spectrometers Detectors and Associated Equipment* 500 (2003), p. 351.

- 1
2
3 [25] S. Zhang, L. Raniero, E. Fortunato, L. Pereira, H. Aguas, L. Ferreira and R. Martins,
4 Amorphous silicon based p-i-i-n structure for color sensor, In: R. W. T. P. C. K. M. C.
5 R. B. R. Collins, Editor, *Symposium on Amorphous and Nanocrystalline Silicon*
6 *Science and Technology held at the 2005 MRS Spring Meeting*, San Francisco, CA
7 (2005).
8
9 [26] P. G. LeComber, A. E. Owen, W. E. Spear, J. Hajto, A. J. Snell, W. K. Choi, M. J.
10 Rose and S. Reynolds, *Journal of Non-Crystalline Solids* 77-8 (1985), p. 1373.
11 [27] E. Fortunato, R. Martins, I. Ferreira, M. Santos, A. Macarico and L. Guimaraes,
12 *Journal of Non-Crystalline Solids* 115 (1989), p. 120.
13 [28] E. Fortunato, G. Lavareda, M. Vieira and R. Martins, *Review of Scientific Instruments*
14 65 (1994), p. 3784.
15 [29] S. Arimoto, H. Yamamoto, H. Ohno and H. Hasegawa, *Journal of Applied Physics* 57
16 (1985), p. 4778.
17 [30] R. Martins, P. Baptista, L. Silva, L. Raniero, G. Doria, R. Franco and E. Fortunato,
18 *Journal of Non-Crystalline Solids* 354 (2008), p. 2580.
19 [31] R. Martins, P. Baptista, L. Raniero, G. Doria, L. Silva, R. Franco and E. Fortunato,
20 *Applied Physics Letters* 90 (2007).
21 [32] R. Martins, H. Aguas, I. Ferreira, E. Fortunato, S. Lebib, P. R. I. Cabarrocas and L.
22 Guimaraes, *Chemical Vapor Deposition* 9 (2003), p. 333.
23 [33] S. Zhang, X. Liao, Y. Xu, R. Martins, E. Fortunato and G. Kong, *Journal of Non-*
24 *Crystalline Solids* 338-40 (2004), p. 188.
25 [34] L. Raniero, H. Aguas, L. Pereira, E. Fortunato, I. Ferreira and R. Martins, *Advanced*
26 *Materials Forum* 455-456 (2004), p. 104.
27 [35] J. P. M. Schmitt, *Journal of Non-Crystalline Solids* 59-6 (1983), p. 649.
28 [36] B. Drevillon, J. Perrin, J. M. Siefert, J. Huc, A. Lloret, G. Derosny and J. P. M.
29 Schmitt, *Applied Physics Letters* 42 (1983), p. 801.
30 [37] R. Martins, J. Figueiredo, V. Silva, H. Aguas, F. Soares, A. Marques, I. Ferreira and E.
31 Fortunato, *Journal of Non-Crystalline Solids* 299 (2002), p. 1283.
32 [38] E. Fortunato, L. Pereira, H. Aguas, I. Ferreira and R. Martins, *Proceedings of the Ieee*
33 93 (2005), p. 1281.
34 [39] T. Tsukada, *Active-Matrix Liquid-Crystal Displays*, in *The Technology and*
35 *applications of amorphous silicon*, R. A. Street, ed., Springer Verlag, NY, 2000, p. 7.
36 [40] R. Martins, A. Macarico, M. Vieira, I. Ferreira and E. Fortunato, *Philosophical*
37 *Magazine B-Physics of Condensed Matter Statistical Mechanics Electronic Optical*
38 *and Magnetic Properties* 76 (1997), p. 249.
39 [41] L. Raniero, I. Ferreira, E. Fortunat and R. Martins, *High Temperature Material*
40 *Processes* 11 (2007), p. 575.
41 [42] J. H. Park, J. B. Choi, H. Y. Kim, K. Y. Lee and J. Y. Lee, *Thin Solid Films* 266
42 (1995), p. 129.
43 [43] H. Aguas, L. Raniero, L. Pereira, E. Fortunato and R. Martins, *Thin Solid Films* 451-
44 52 (2004), p. 264.
45 [44] H. E. Kissinger, *Analytical Chemistry* 29 (1957), p. 1702.
46 [45] L. Raniero, I. Ferreira, H. Aguas, S. Zhang, E. Fortunato and R. Martins, Study of a-
47 SiC : H buffer layer on nc-Si/a-Si : H solar cells deposited by PECVD technique,
48 *Conference Record of the Thirty-First Ieee Photovoltaic Specialists Conference - 2005*
49 (2005).
50 [46] S. Guha, *Multijunction Solar Cells and Modules in Technology and applications of*
51 *amorphous silicon.*, R. A. Street, ed., Springer, NY, 2000, p. 252.
52 [47] R. Martins, I. Ferreira, H. Aguas, V. Silva, E. Fortunato and L. Guimaraes, *Solar*
53 *Energy Materials and Solar Cells* 73 (2002), p. 39.
54
55
56
57
58
59
60

- 1
2
3 [48] L. Raniero, S. Zhang, H. Aguas, I. Ferreira, R. Igreja, E. Fortunato and R. Martins,
4 Thin Solid Films 487 (2005), p. 170.
5
6 [49] J. Springer, B. Rech, W. Rietz, J. Muller and M. Vanecek, Solar Energy Materials and
7 Solar Cells 85 (2005), p. 1.
8 [50] R. Martins and E. Fortunato, Journal of Applied Physics 78 (1995), p. 3481.
9 [51] E. Fortunato, F. Soares, P. Teodoro, N. Guimaraes, M. Mendes, H. Aguas, V. Silva
10 and R. Martins, Thin Solid Films 337 (1999), p. 222.
11 [52] H. Aguas, L. Pereira, L. Raniero, D. Costa, E. Fortunato and R. Martins, Journal of
12 Non-Crystalline Solids 352 (2006), p. 1787.
13 [53] L. Pereira, P. Barquinha, E. Fortunato, R. Martins, D. Kang, C. J. Kim, H. Lim, I.
14 Song and Y. Park, Thin Solid Films 516 (2008), p. 1544.
15 [54] P. R. I. Cabarrocas, A. F. I. Morral, S. Lebib and Y. Poissant, Pure and Applied
16 Chemistry 74 (2002), p. 359.
17 [55] E. Fortunato, A. Goncalves, A. Marques, A. Pimentel, P. Barquinha, H. Aguas, L.
18 Pereira, L. Raniero, G. Goncalves, I. Ferreira and R. Martins, Advanced Materials
19 Forum 514-516 (2006), p. 3.
20 [56] E. Fortunato, V. Assuncao, A. Marques, A. Goncalves, H. Aguas, L. Pereira, I.
21 Ferreira, F. M. B. Fernandes, R. J. C. Silva and R. Martins, Advanced Materials
22 Forum 455-456 (2004), p. 12.
23 [57] E. Fortunato, A. Goncalves, V. Assuncao, A. Marques, H. Aguas, L. Pereira, I.
24 Ferreira and R. Martins, Thin Solid Films 442 (2003), p. 121.
25 [58] L. Raniero, I. Ferreira, A. Pimentel, A. Goncalves, P. Canhola, E. Fortunato and R.
26 Martins, Thin Solid Films 511 (2006), p. 295.
27 [59] H. Aguas, V. Silva, E. Fortunato, S. Lebib, P. R. I. Cabarrocas, I. Ferreira, L.
28 Guimaraes and R. Martins, Japanese Journal of Applied Physics Part 1-Regular Papers
29 Short Notes & Review Papers 42 (2003), p. 4935.
30 [60] R. Martins, V. Silva, I. Ferreira, A. Domingues and E. Fortunato, Vacuum 56 (2000),
31 p. 25.
32 [61] R. Martins, H. Aguas, I. Ferreira, E. Fortunato, L. Raniero and P. R. I. Cabarrocas,
33 Advanced Materials Forum 455-456 (2004), p. 100.
34 [62] T. Ohira, O. Ukai and M. Noda, Surface Science 458 (2000), p. 216.
35 [63] E. Fortunato, L. Raniero, L. Silva, A. Goncalves, A. Pimentel, P. Barquinha, H.
36 Aguas, L. Pereira, G. Goncalves, I. Ferreira, E. Elangovan and R. Martins, Solar
37 Energy Materials and Solar Cells 92 (2008), p. 1605.
38 [64] P. Kumar, F. Zhu and A. Madan, Electrical and structural properties of nano-
39 crystalline silicon intrinsic layers for nano-crystalline silicon solar cells prepared by
40 very high frequency plasma chemical vapor deposition, *Symposium on Materials in
41 Clean Power Systems II held at the 2007 TMS Annual Conference and Exposition,*
42 *Orlando, FL (2008).*
43 [65] A. Stavrides, A. Kunrath, J. Hu, R. Treglio, A. Feldman, B. Marsen, B. Cole, E. Miller
44 and A. Madan, Use of amorphous silicon tandem junction solar cells for hydrogen
45 production in a photoelectrochemical cell, In: L. Vayssieres, Editor, *Conference on
46 Solar Hydrogen and Nanotechnology*, San Diego, CA (2006).
47 [66] C. S. Jiang, B. Yan, Y. Yan, C. W. Teplin, R. Reedy, H. R. Moutinho, M. M. Al-
48 Jassim, J. Yang and S. Guha, Effect of P incorporation on aggregation of
49 nanocrystallites in amorphous and nanocrystalline mixed-phase silicon thin films,
50 *22nd International Conference on Amorphous and Nanocrystalline Semiconductors,*
51 *Breckenridge, CO (2007).*
52 [67] S. Guha, Manufacturing technology of amorphous and nanocrystalline silicon solar
53 cells, In: K. L. S. D. K. Narasimhan, Editor, *14th International Workshop on the*
54
55
56
57
58
59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- Physics of Semiconductor Devices*, Mumbai, INDIA (2007).
- [68] C. S. Jiang, B. Yan, H. R. Moutinho, M. M. Al-Jassim, J. Yang and S. Guha, Light soaking and thermal annealing effects on the micro-electrical properties of amorphous and nanocrystalline mixed-phase silicon solar cells, In: V. M. S. N. A. Y. J. Z. H. W. Chu, Editor, *Symposium on Amorphous and Polycrystalline Thin-Film Silicon Science and Technology held at the 2007 MRS Spring Meeting*, San Francisco, CA (2007).
- [69] B. Yan, G. Yue and S. Guha, Status of nc-Si : H solar cells at United Solar and roadmap for manufacturing a-Si : H and ne-Si : H based solar panels, In: V. M. S. N. A. Y. J. Z. H. W. Chu, Editor, *Symposium on Amorphous and Polycrystalline Thin-Film Silicon Science and Technology held at the 2007 MRS Spring Meeting*, San Francisco, CA (2007).
- [70] R. Martins and E. Fortunato, *Thin Film Position Sensitive Detectors: From 1D to 3D Applications in Technology and applications of amorphous silicon*, R. A. Street, ed., Springer, NY, 2000, p. 342.
- [71] F. E. Martins R., *Amorphous silicon Position Sensors*, in *The Technology and Applications of Amorphous Silicon*, R. Street, ed., Springer Verlag, NY, 2000, p. 342.
- [72] J. E. Harvey, *Handbook of Optics*, McGraw-Hill, Inc, New York (1995).
- [73] K. Parikh, K. Chung, B. Choi, J. C. Goh, J. M. Huh, Y. R. Song, N. Kim and J. Choi, Novel AC bias compensation scheme in hydrogenated amorphous silicon TFT for AMOLED Displays, *6th International Meeting on Information Displays/5th International Display Manufacturing Conference (IMID/IDMC 2006)*, Daegu, SOUTH KOREA (2006).
- [74] S. F. Lin, A. J. Flewitt, W. I. Milne, R. B. Wehrspohn and M. J. Powell, Applied Physics Letters 86 (2005).
- [75] R. B. Wehrspohn, M. J. Powell and S. C. Deane, Journal of Applied Physics 93 (2003), p. 5780.
- [76] M. J. Powell, R. B. Wehrspohn and S. C. Deane, Nature of metastable and stable dangling bond defects in hydrogenated amorphous silicon, *19th International Conference on Amorphous and Microcrystalline Semiconductors (ICAMS 19)*, Old Nice, France (2001).
- [77] B. Stannowski, R. E. I. Schropp, R. B. Wehrspohn and M. J. Powell, Amorphous-silicon thin-film transistors deposited by VHF-PECVD and hot-wire CVD, *19th International Conference on Amorphous and Microcrystalline Semiconductors (ICAMS 19)*, Old Nice, France (2001).
- [78] B. Hekmatshoar, K. H. Cherenack, A. Z. Kattamis, K. Long, S. Wagner and J. C. Sturm, Applied Physics Letters 93 (2008).
- [79] K. Ishibashi and M. Matsumura, Applied Physics Letters 41 (1982), p. 454.
- [80] I. C. Cheng and S. Wagner, Self-aligned nanocrystalline silicon thin-film transistor with deposited n(+) source/drain layer, In: V. M. S. N. A. Y. J. Z. H. W. Chu, Editor, *Symposium on Amorphous and Polycrystalline Thin-Film Silicon Science and Technology held at the 2007 MRS Spring Meeting*, San Francisco, CA (2007).
- [81] M. R. Esmaili-Rad, A. Sazonov and A. Nathan, Journal of Applied Physics 103 (2008).
- [82] A. Ahnood, K. Ghaffarzadeh, A. Nathan, P. Servati, F. Li, M. R. Esmaili-Rad and A. Sazonov, Applied Physics Letters 93 (2008).
- [83] E. B. K. Chan, D. Knipp, H. Stiebig, Semiconductor Science and Technology 22 (2007), p. 1213.

Figure Captions

Figure 1. (a) Image of the 128 psd integrated array and of the (b) pcb where it will be mounted

Figure 2. (a) Schematic of the electrical interconnections between the sensor; the controller unit; the MX4 and the Computer where the acquisition data board exists; (b) Global vision of the line inspection camera demonstrator used; (c) detailed information about the optical system. The numbers refer to: 1) Chassis; 2) pcb board that contains the sensor; 3) Lens (35-70 mm, f:1.4); 4) Laser line generator (635 nm)+ angular adjustment; 5) Connecting cable from the pcb board to the PC; 6) X-Y controlled table.

Figure 3. Schematic structure of bottom gate ns-Si:H TFTs integrating as dielectric: (a) aluminum oxide/titanium oxide multilayer (ATO) deposited by ALD; (b) thermal silicon oxide (SiO_2); (c) sputtered hafnium oxide (HfO_2)

Figure 4. Micro-Raman spectra for the different set of silicon thin films produced.

Figure 5. Hydrogen evolution spectra for the set of silicon thin films processed. The illustrations shown aim to represent the atoms rearrangements within the different type of structures studied: a) microcrystalline films; b) nanostructured films; c) amorphous films.

Figure 6. Power density as a function of hydrogen dilution ratio used, showing the different conditions that lead to the production of materials where the amorphous or the microcrystalline phases dominate. In-between we can see the transition region.

Figure 7. Evolution of LT and HT hydrogen exodiffusion peak positions as function of power density, for $d_r=5\%$.

Figure 8. (a) Cross section of the solar cell structure; (b) J-V characteristic of the solar cell; (c) quantum efficiency curve for the produced solar cell.

Figure 9. Spatial resolution measurements performed on a sensor with 0.25 μm and 1.00 μm steps.

Figure 10. (a) Transfer characteristics on linear regime for ns-Si:H TFT produced with the protection grid integrating different dielectrics; also plotted is the corresponding

1
2
3 transconductance; (b) transfer characteristics on linear ($V_{DS}=1V$) and saturation regimes
4 ($V_{DS}=10V$) for ns-Si:H TFT with different channel dimensions integrating SiO_2 as
5 dielectric. The plot of the transconductance for both channel lengths analysed is also
6 shown.
7
8
9

10
11
12 Figure 11. Activation energy for nanostructured films processed in the transition region. Data
13 from Figure 8 were fitted by equation 2.
14

15
16 Figure 12. Schematic of the light line projected onto de integrated 128 psd arrays that
17 contain the information of the object to be displayed.
18

19
20 Figure 13. MTF (%) as a function of the spatial frequency.
21

22
23
24 Figure 14. (a) Image to be 3D scanned, showing the laser line projected on it; (b) collected
25 image by the sensor, in real time, without any type of data treatment.
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Table 1

Layers	Thickness (nm)	Conductivity ($\Omega^{-1}\text{cm}^{-1}$)	Optical Gap (eV)
p-doped	$\approx 7,8\pm 2$ nm	$3,2\times 10^{-6}$	$1,94\pm 0,01$
Buffer ₁	$\approx 0,5$ nm	-----	$1,88\pm 0,01$
Buffer ₂	$\approx 0,8$ nm	-----	$1,84\pm 0,01$
Intrinsic	$\approx 270\pm 10$ nm	$6,12\times 10^{-10}$	$1,82\pm 0,01$
n-doped	$\approx 25\pm 5$ nm	$2,46\times 10^{-3}$	1,80
Back contact	≈ 30 nm of Ag + ≈ 170 nm of Al	-----	-----
Gas mixture used: p-layer = 1% $(\text{CH}_4)_3\text{B}_2$ +40% CH_4 +39% SiH_4 +20% H_2 ; Buffer ₁ = 7% SiH_4 +8% CH_4 +85% H_2 Buffer ₂ = 7% SiH_4 +4% CH_4 +89% H_2		i-layer = 5% SiH_4 +95% H_2 n-layer = 1% PH_3 +30% SiH_4 +28% H_2 +41%He	

Table 2.

Array type	Dimension [mm]	Active area [mm]	Non-linearity [%]	Line resolution [μm]	Working Light wave number range [nm]	Frequency response [kHz]	NEP [$\text{W}/\text{Hz}^{1/2}$]
128	<i>Chip carrier</i> 47×47 <i>Sensor</i> 30×30	20×12	< 2%	< 0.75	500-680	> 500	10^{-11}

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

For Peer Review Only

Table 3.

Open space distance (h)	40-6 cm
Working range	10-0.5 cm
Sensor Deep resolution (z)	2.5-0.75 μm
Sensor horizontal resolution (x)	50-10 μm
Scanning speed (v_y)	<50 cm/s
Frequency response	> 500 kHz
Linearity	> 99,9%
Lens aperture	2.8

Table 4.

Dielectric	μ_{FE} ($\text{cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$)	V_T (V)	S (V/dec)	I_{on}/I_{off}
ATO	1.14	2.04	0.52	$>10^6$
SiO ₂	1.24	2.35	0.45	$>10^7$
HfO ₂	0.85	5.19	0.63	$>10^7$

Table 5.

W/L (μm)	μ_{FE} ($\text{cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$)	V_T (V)	S (V/dec)	I_{on}/I_{off}
15/15	1.24	2.35	0.45	$>10^7$
50/50	1.84	2.82	0.56	$>10^6$
50/50 OG*	2.47	2.78	0.32	$>10^7$

* device produced using a grid with a larger aperture than the other

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

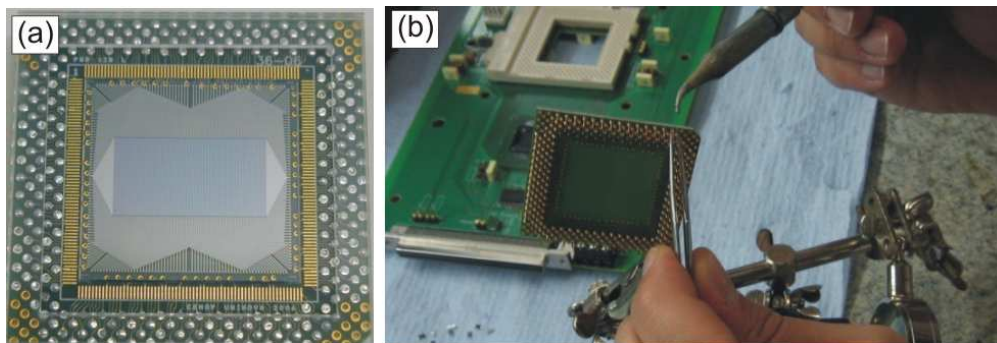


Figure 1. (a) Image of the 128 psd integrated array and of the (b) pcb where this will be mounted

Peer Review Only

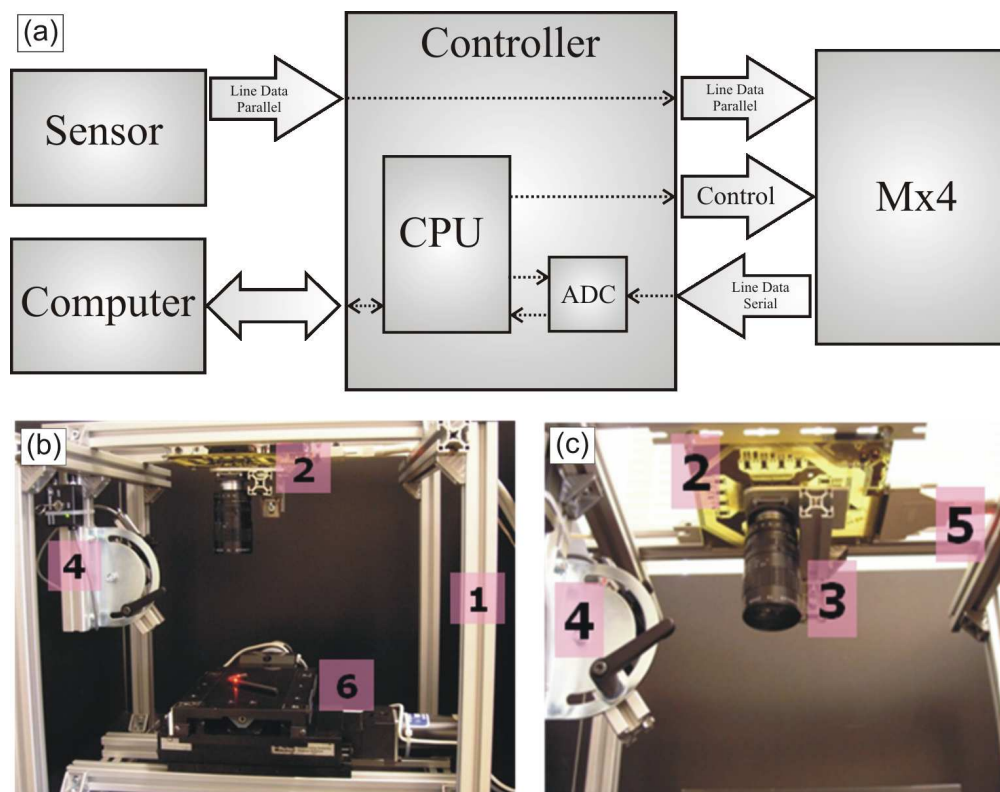


Figure 2. (a) Schematic of the electrical interconnections between the sensor; the controller unit; the MX4 and the Computer where it exists the acquisition data board; (b) Global vision of the line inspection camera demonstrator used; (c) detailed information about the optical system. The numbers refer to: 1) Chassis; 2) pcb board that contains the sensor; 3) Lens (35-70 mm, f:1.4); 4) Laser line generator (635 nm)+ angular adjustment; 5) Connecting cable from the pcb board to the PC; 6) X-Y controlled table.

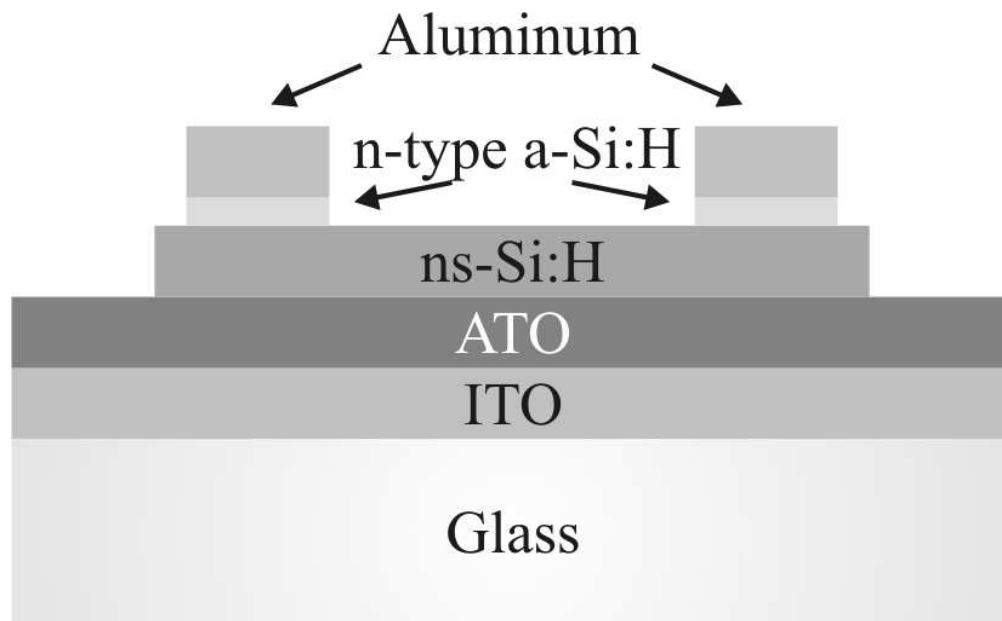


Figure 3. Schematic structure of bottom gate ns-Si:H TFTs integrating as dielectric: (a) aluminum oxide/titanium oxide multilayer (ATO) deposited by ALD;

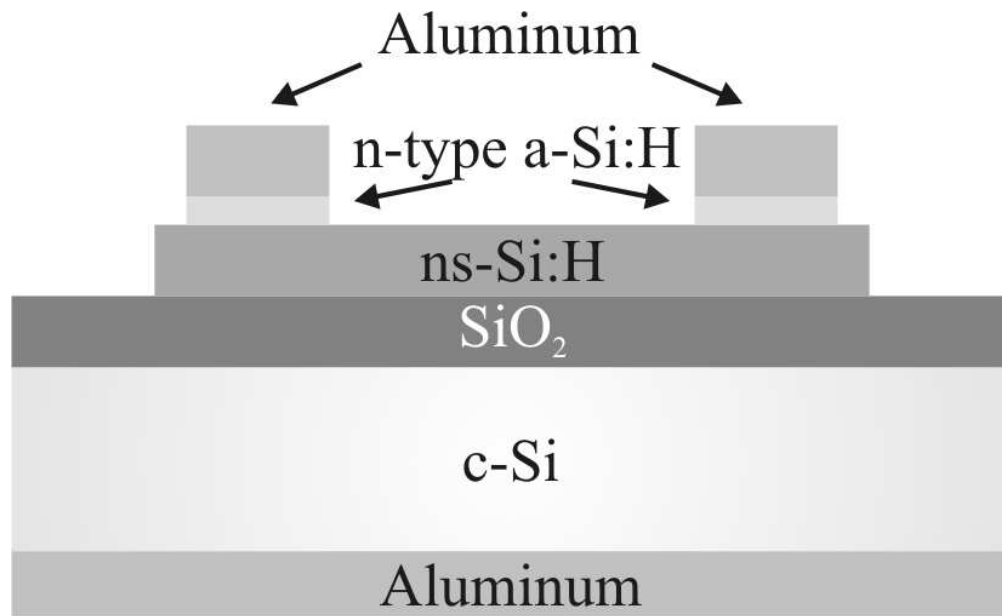


Figure 3. Schematic structure of bottom gate ns-Si:H TFTs integrating as dielectric: (b) thermal silicon oxide (SiO₂);

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60


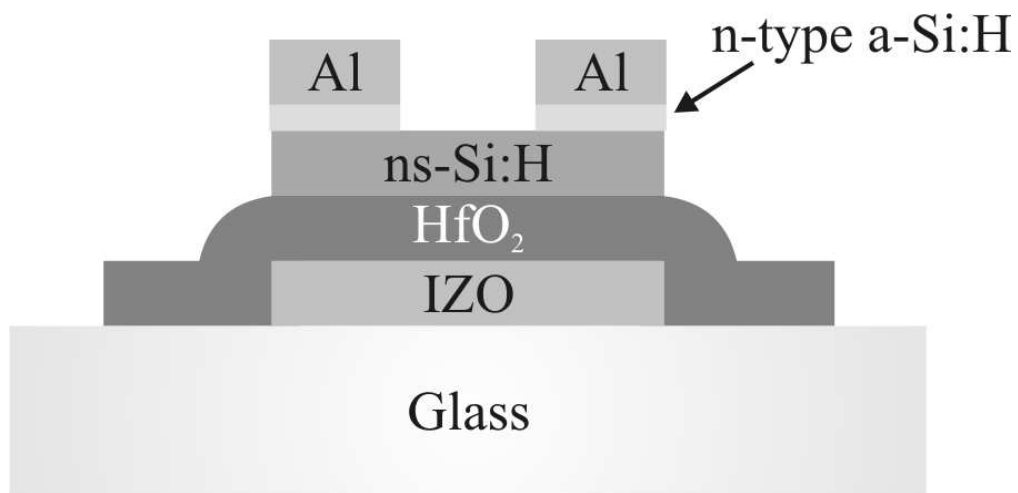


Figure 3. Schematic structure of bottom gate ns-Si:H TFTs integrating as dielectric: (c) sputtered hafnium oxide (HfO₂)

Review Only

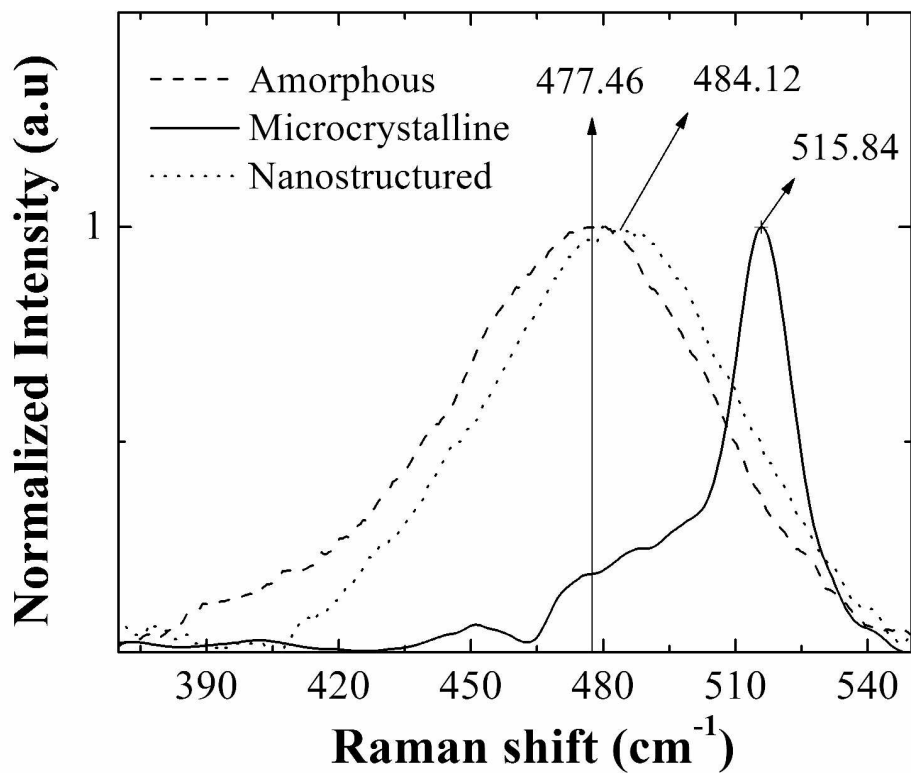

33 Figure 4. Micro-Raman spectra for the different set of silicon thin films produced.
34 269x206mm (300 x 300 DPI)

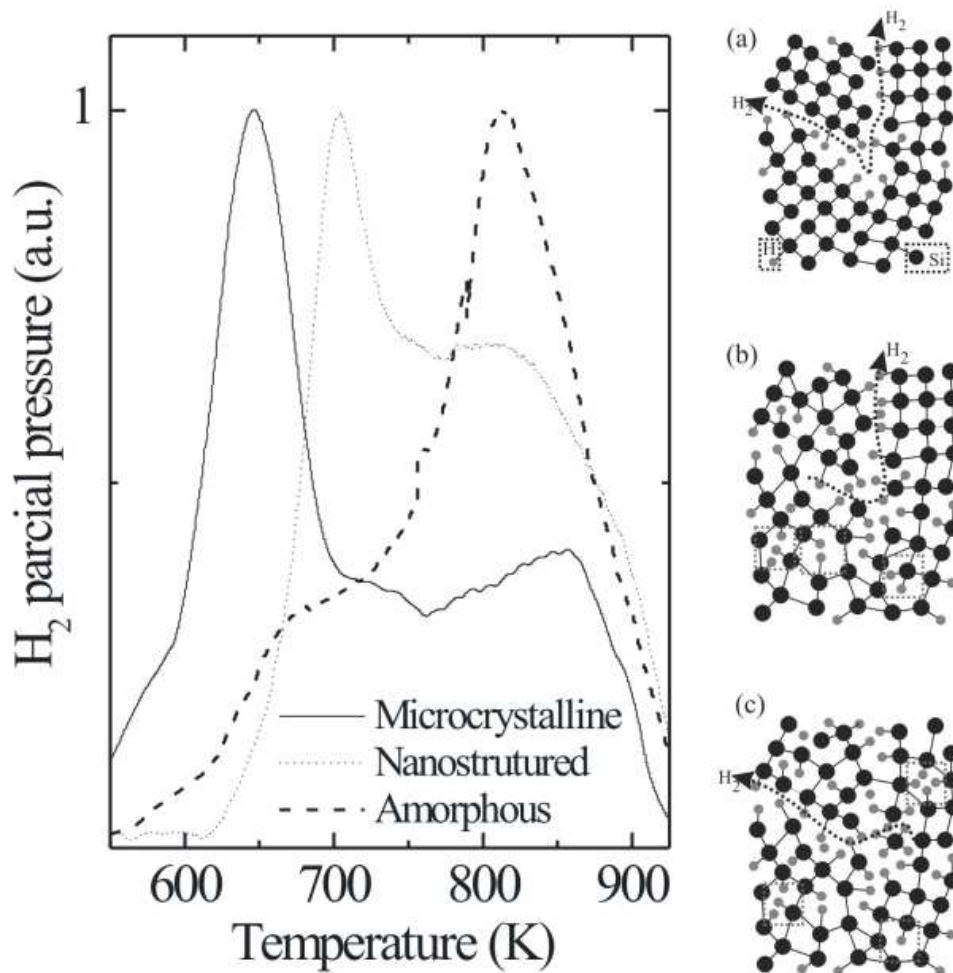


Figure 5. Hydrogen evolution spectra for the set of silicon thin films processed. The illustrations shown aim to represent the atoms rearrangements within the different type of structures studied: a) microcrystalline films; b) nanostructured films; c) amorphous films.

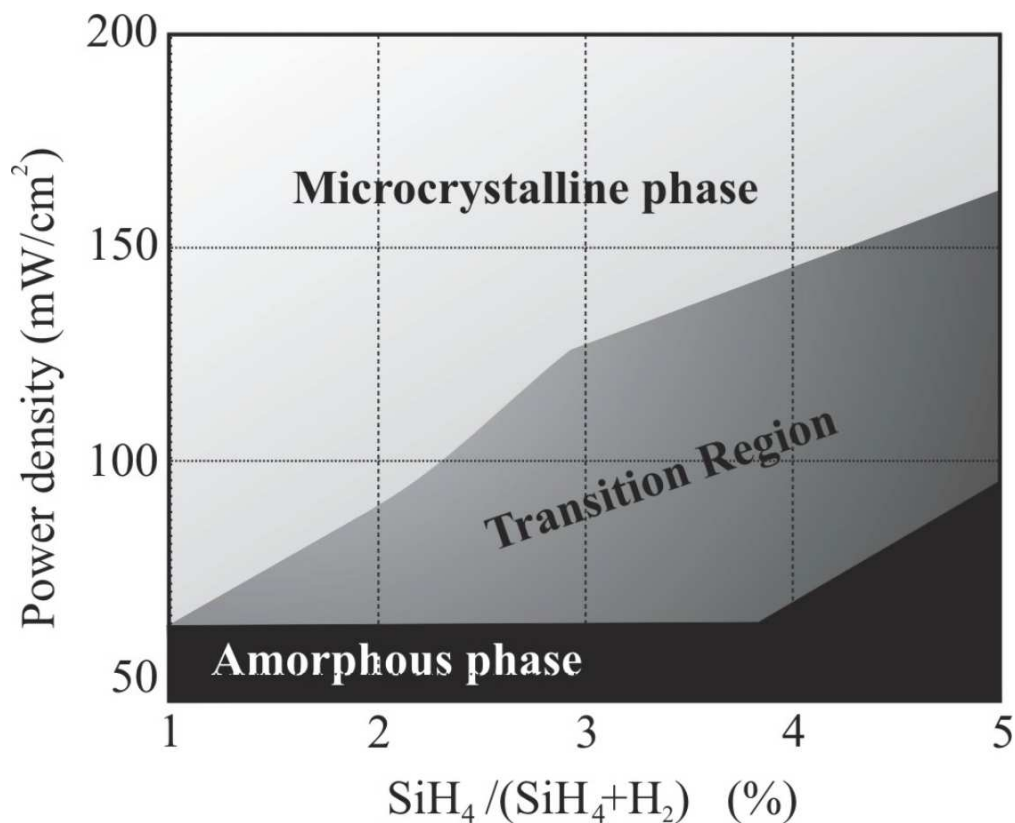


Figure 6. Power density as a function of hydrogen dilution ratio used, showing the different conditions that lead to the production of materials where the amorphous or the microcrystalline phases dominate. In-between we can see the transition region.

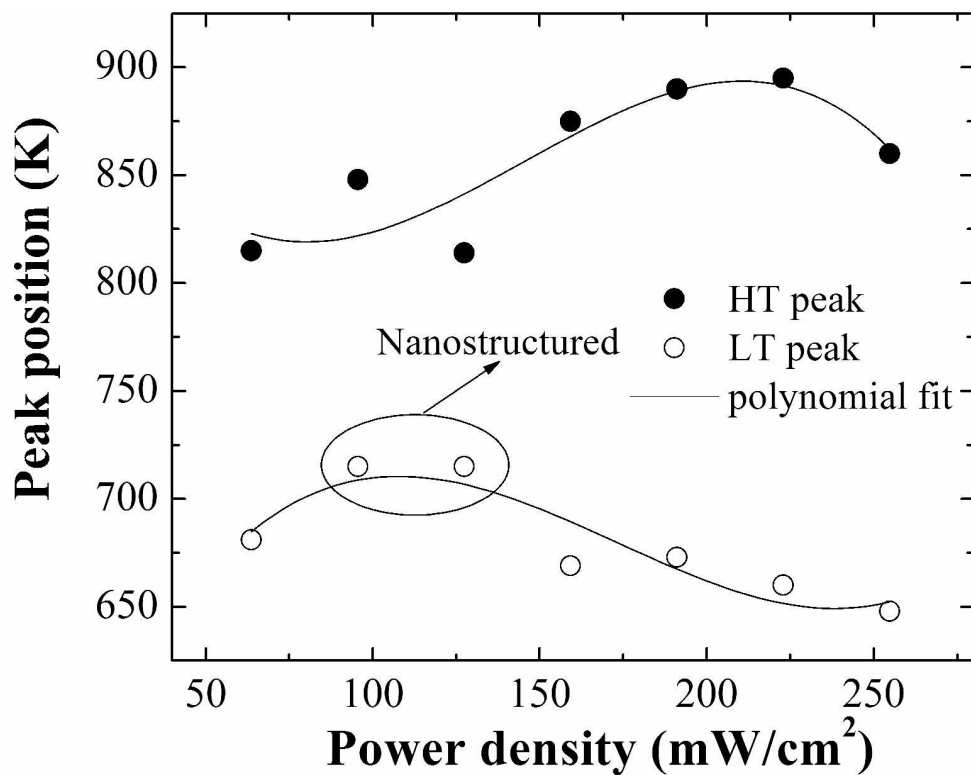


Figure 7. Evolution of LT and HT hydrogen exodiffusion peak positions as function of power density, for $dr=5\%$.
269x206mm (300 x 300 DPI)

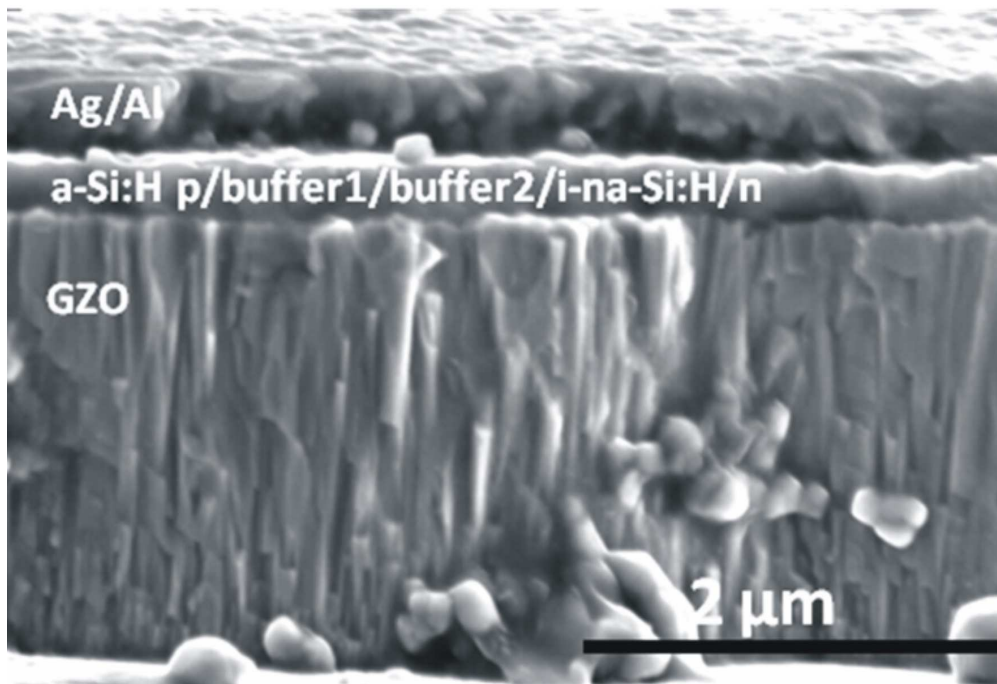


Figure 8. (a) Cross section of the solar cell structure;

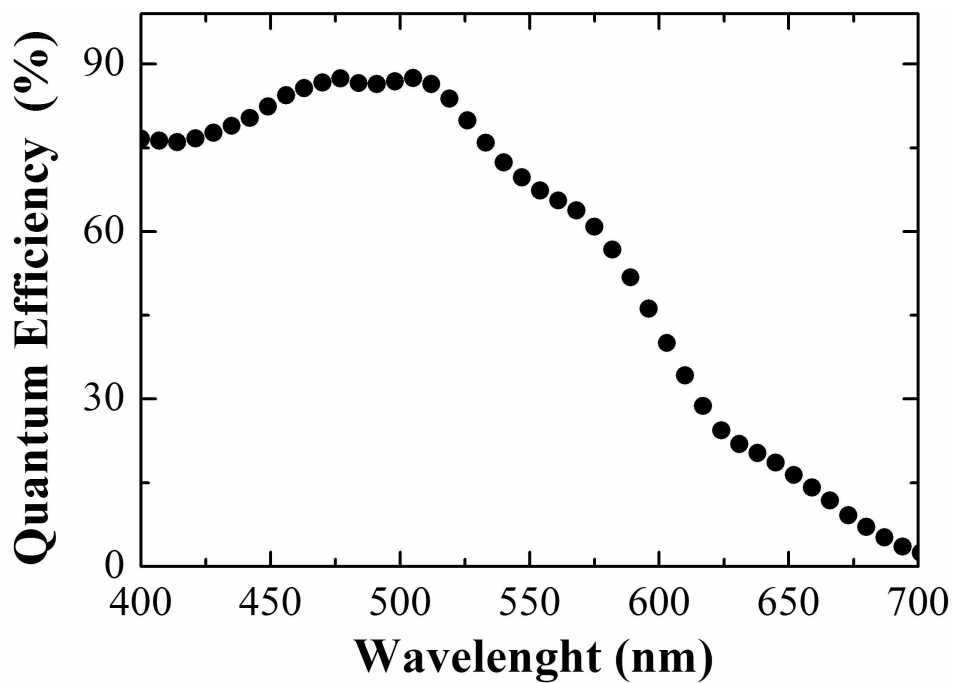


Figure 8. b) J-V characteristic of the solar cell;
226x152mm (300 x 300 DPI)

view Only

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

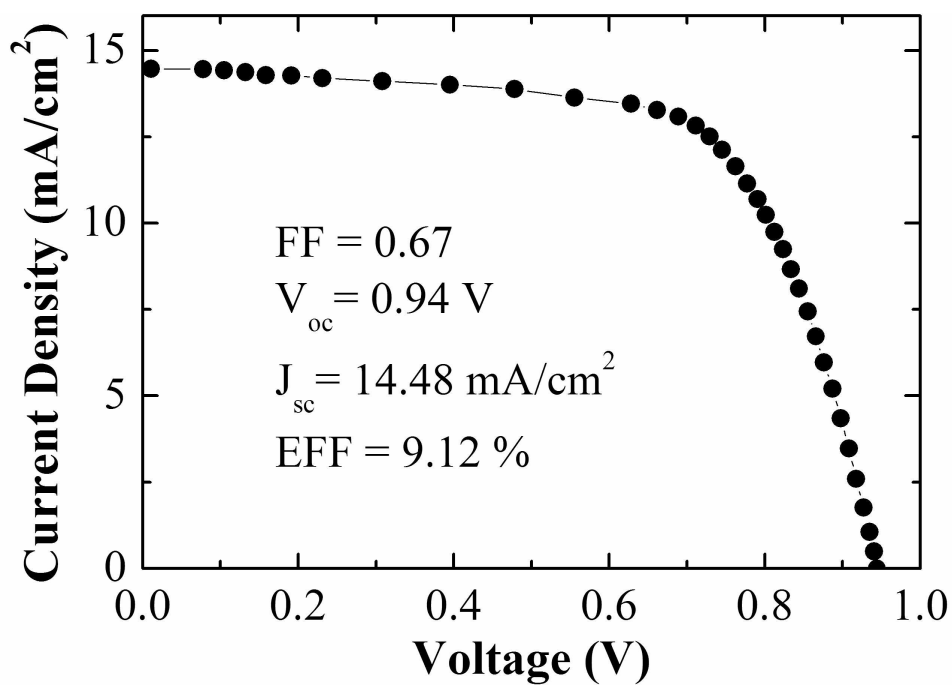


Figure 8. c) the quantum efficiency curve for the solar cell produced.
226x152mm (300 x 300 DPI)

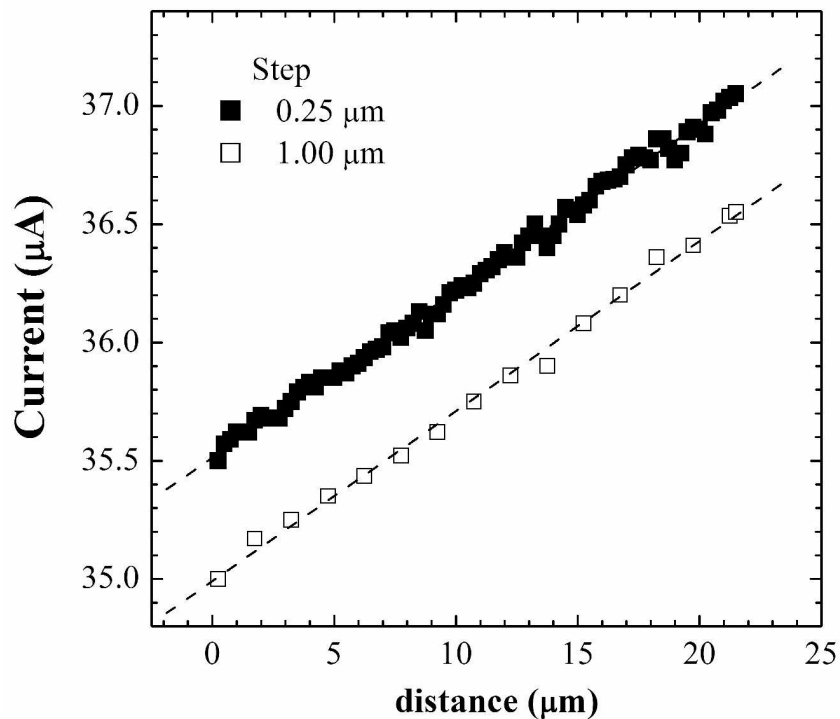


Figure 9. Spatial resolution measurements performed on a sensor with 0.25 µm and 1.00 µm steps. 266x206mm (300 x 300 DPI)


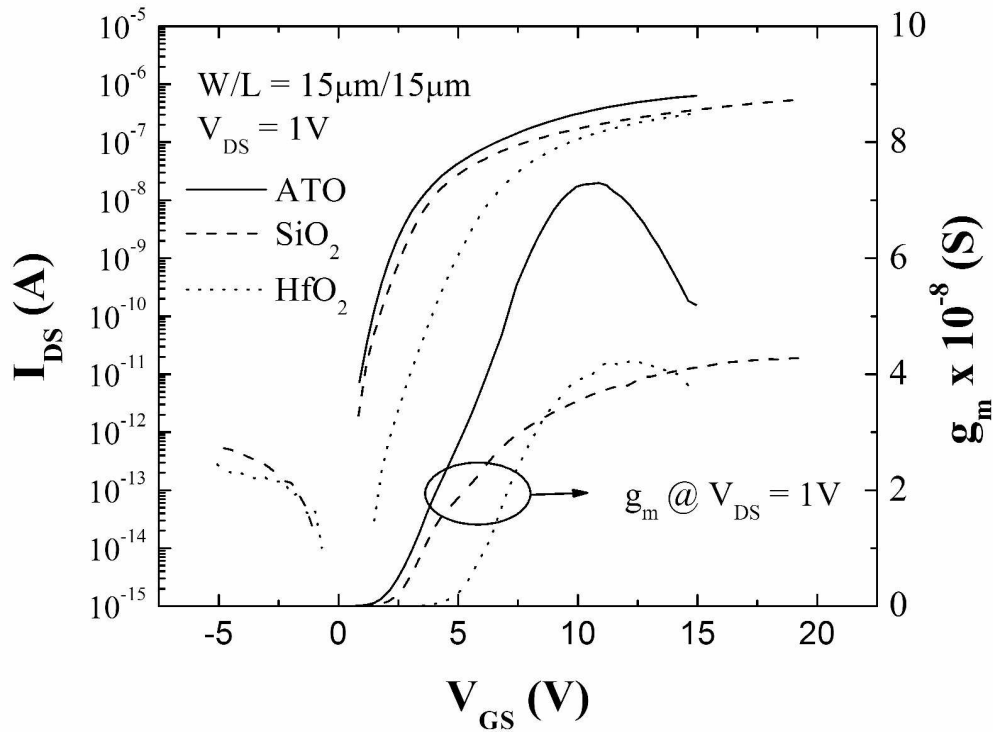


Figure 10. (a) Transfer characteristics on linear regime for ns-Si:H TFT produced with the protection grid integrating different dielectrics. There it is also plotted the corresponding transconductance; (b) transfer characteristics on linear ($V=1V$) and saturation regimes ($V=10V$) for ns-Si:H TFT with different channel dimensions integrating

SiO as dielectric. There, it is also shown the plot of the transconductance for both channel lengths analysed.


269x206mm (300 x 300 DPI)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

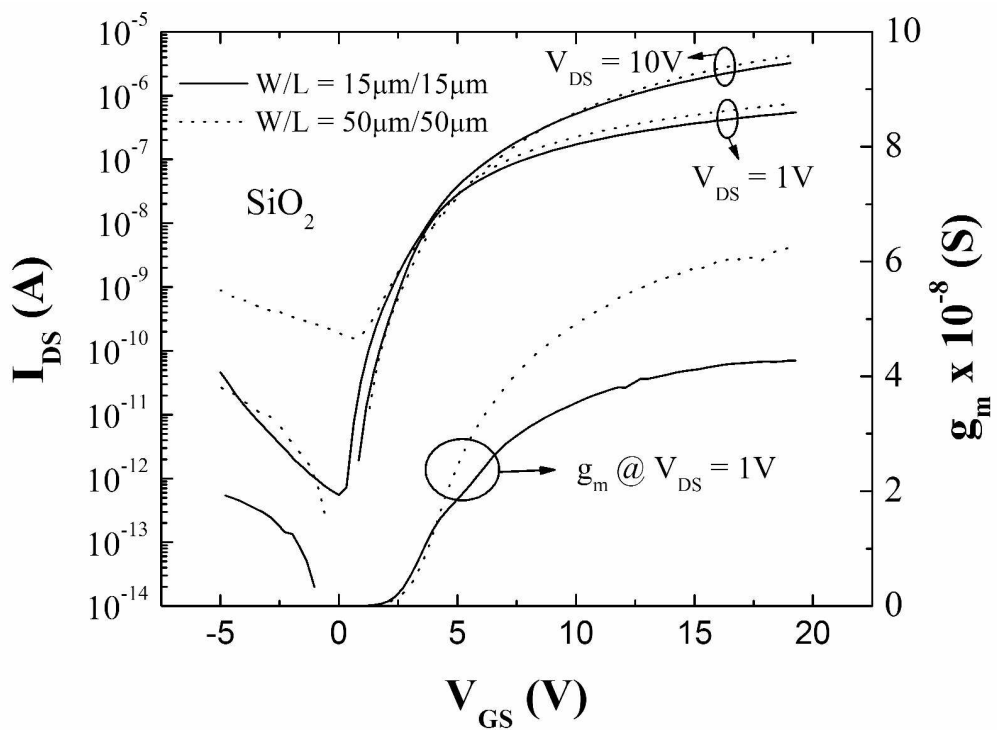

269x206mm (300 x 300 DPI)

Pre-proof Only

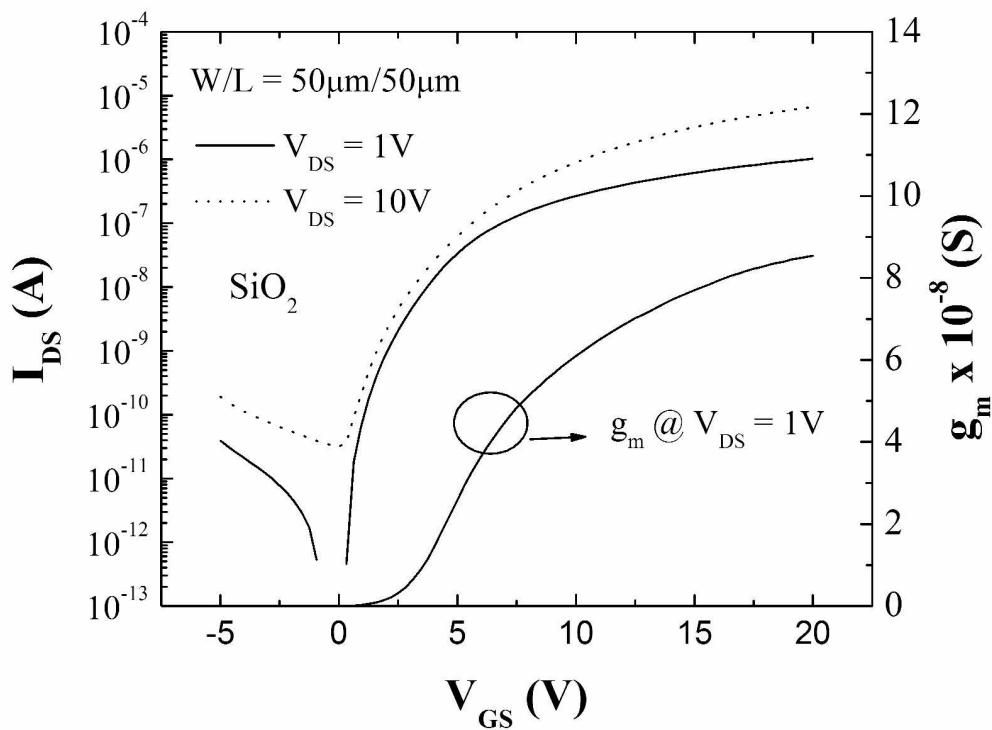

269x206mm (300 x 300 DPI)

Pre-proof Only

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60


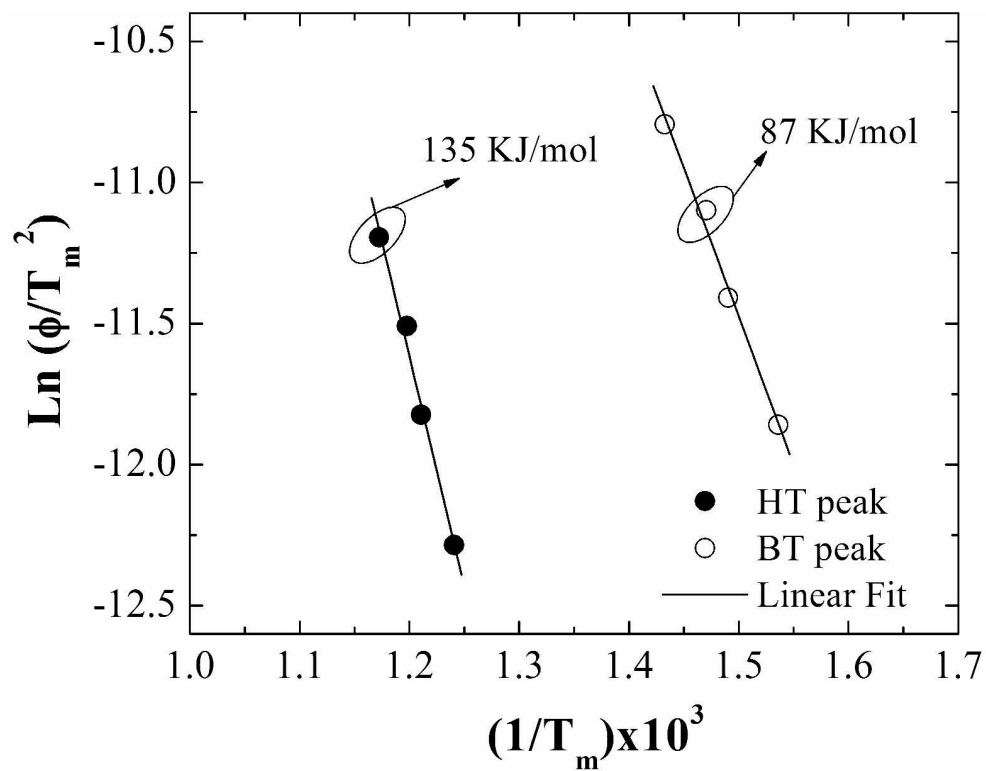


Figure 11. Activation energy for nanostructured films processed in the transition region. Data from Figure 8 were fitted by equation 2.
269x206mm (300 x 300 DPI)

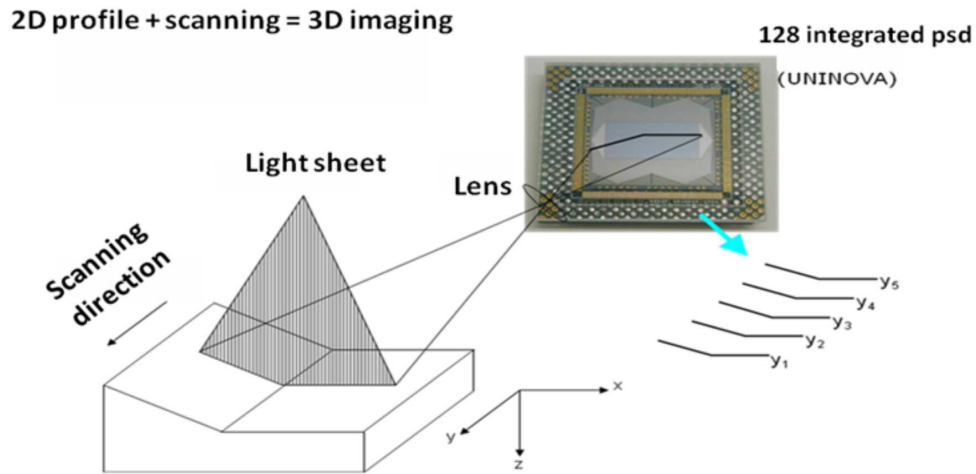

25 Figure 12. Schematic of the light line projected onto de integrated 128 psd arrays that contains the
26 information of the object to be displayed.

27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Review Only

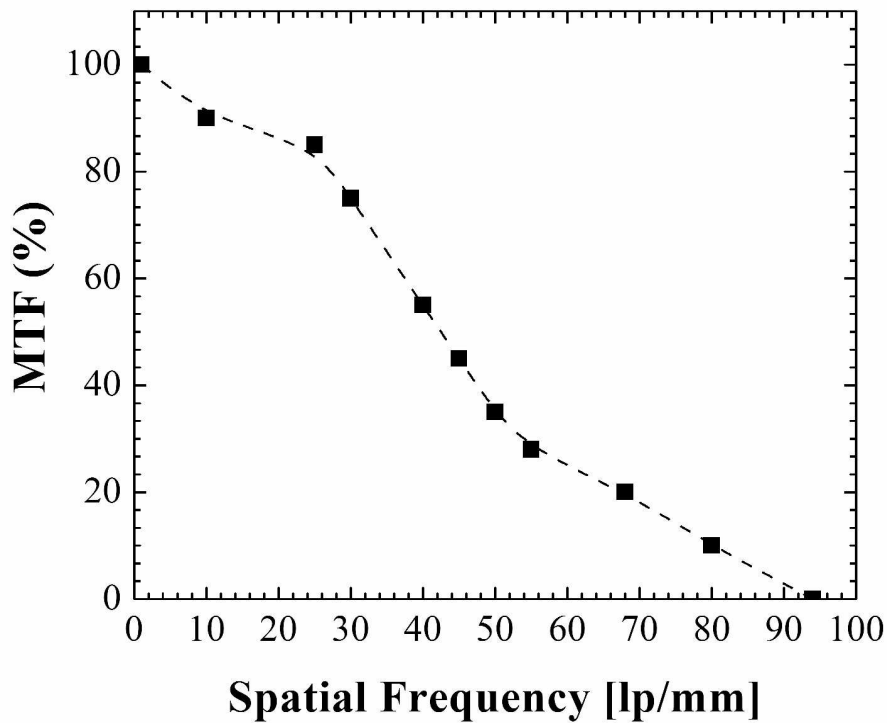


Figure 13. MTF (%) as a function of the spatial frequency.
269x207mm (300 x 300 DPI)

Pre-proof Only

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

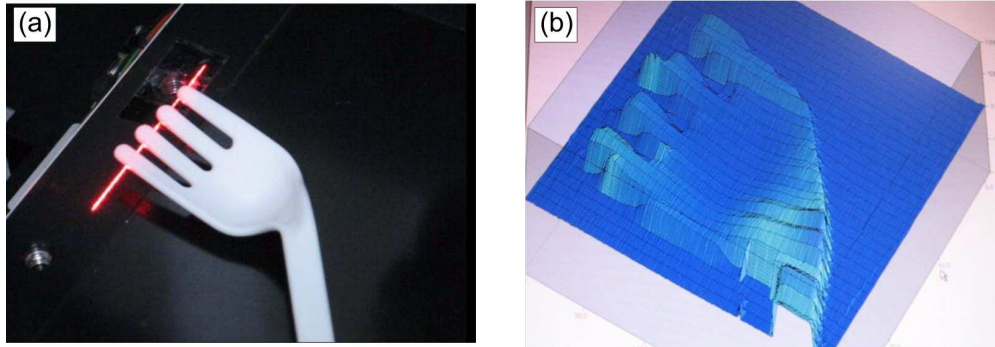


Figure 14. (a) Image to be 3D scanned, showing the laser line projected on it; (b) collected image by the sensor, in real time, without any type of data treatment.

Peer Review Only