



HAL
open science

A thermoreversible supramolecular hydrogel inspired by poly(N,N-dimethylacrylamide)

Pablo Casuso, Iraida Loinaz, Marco Möller, Pedro Carrasco, José Adolfo Pomposo, Hans Jurgen Grande, Ibon Odriozola

► **To cite this version:**

Pablo Casuso, Iraida Loinaz, Marco Möller, Pedro Carrasco, José Adolfo Pomposo, et al.. A thermoreversible supramolecular hydrogel inspired by poly(N,N-dimethylacrylamide). *Supramolecular Chemistry*, 2009, 21 (07), pp.581-584. 10.1080/10610270802588277 . hal-00520013


HAL Id: hal-00520013

<https://hal.science/hal-00520013>

Submitted on 22 Sep 2010

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

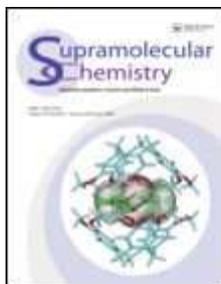


A thermoreversible supramolecular hydrogel inspired by poly(N,N-dimethylacrylamide)

| | |
|--|--|
| Journal: | <i>Supramolecular Chemistry</i> |
| Manuscript ID: | GSCH-2008-0090.R1 |
| Manuscript Type: | Communications |
| Date Submitted by the Author: | 29-Sep-2008 |
| Complete List of Authors: | Casuso, Pablo; CIDETEC, New Materials Department Loinaz, Iraida; CIDETEC, New Materials Department Möller, Marco; CIC BiomaGUNE Carrasco, Pedro; CIDETEC, New Materials Department Pomposo, José; CIDETEC, New Materials Department Grande, Hans; CIDETEC, New Materials Department Odriozola, Ibon; CIDETEC |
| Keywords: | self-assembly, hydrogels, silver, thiolates |
| <p>Note: The following files were submitted by the author for peer review, but cannot be converted to PDF. You must view these files (e.g. movies) online.</p> | |
| Scheme 1.cdx | |



A thermoreversible supramolecular hydrogel inspired by poly(*N,N*-dimethylacrylamide)


Pablo Casuso, Iraida Loinaz, Marco Möller, Pedro Carrasco, José A. Pomposo, Hans J. Grande and Ibon Odriozola*

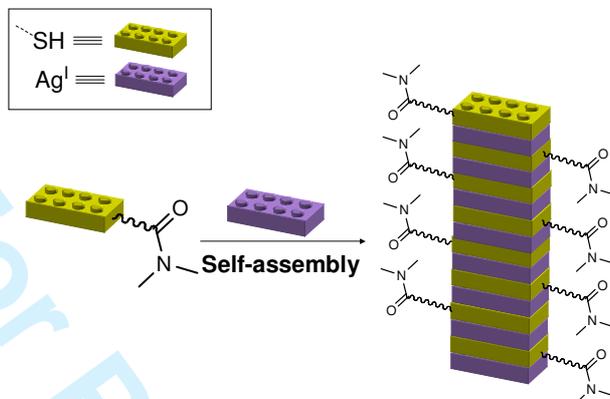

A thermoreversible supramolecular hydrogel based on a silver(I) alkanethiolate bearing terminal *N,N*-dimethylamide groups has been prepared, which is inspired by poly(*N,N*-dimethylacrylamide) (PDMA). This demonstrates the possibility of designing supramolecular hydrogels inspired on conventional polymers, through the self-assembly of the corresponding mercapto-modified monomers promoted by the addition of a Ag^{I} salt.


A thermoreversible supramolecular hydrogel inspired by poly(*N,N*-dimethylacrylamide)

Pablo Casuso, Iraida Loinaz, Marco Möller, Pedro Carrasco, José A. Pomposo, Hans J. Grande and Ibon Odriozola*

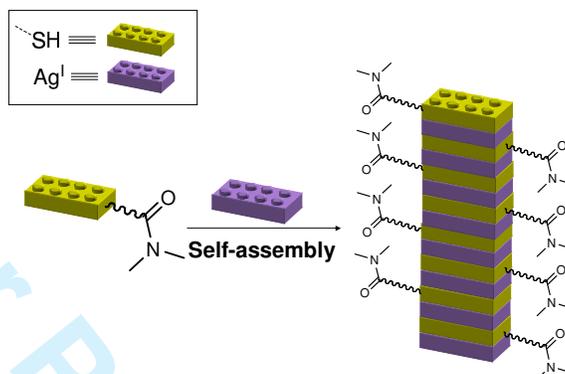

A thermoreversible supramolecular hydrogel based on a silver(I) alkanethiolate bearing terminal *N,N*-dimethylamide groups has been prepared, which is inspired by poly(*N,N*-dimethylacrylamide) (PDMA). This demonstrates the possibility of designing supramolecular hydrogels inspired on conventional polymers, through the self-assembly of the corresponding mercapto-modified monomers promoted by the addition of a Ag^I salt.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

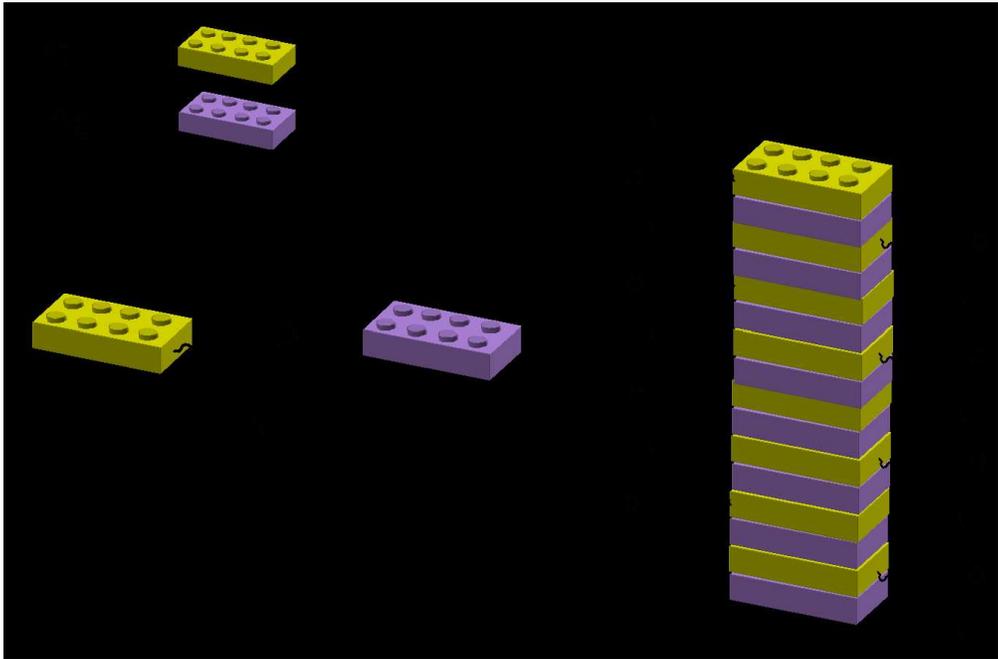

228x150mm (150 x 150 DPI)

Review Only

COMMUNICATION

A thermoreversible supramolecular hydrogel inspired by poly(*N,N*-dimethylacrylamide)

Pablo Casuso,^a Iraida Loinaz,^a Marco Möller,^b Pedro Carrasco,^a José A. Pomposo,^a
Hans J. Grande^a and Ibon Odriozola^{*a}

^a*CIDETEC Centre for Electrochemical Technologies, New Materials Department, Parque Tecnológico de San Sebastián, Paseo Miramón 196, 20009 Donostia-San Sebastián, Spain;* ^b*CIC biomaGUNE, Parque Tecnológico de San Sebastián, Paseo Miramón 182, 20009 Donostia-San Sebastián, Spain*

A thermoreversible supramolecular hydrogel based on a silver(I) alkanethiolate bearing terminal *N,N*-dimethylamide groups has been prepared, which is inspired by poly(*N,N*-dimethylacrylamide) (PDMA). This demonstrates the possibility of designing supramolecular hydrogels inspired by conventional polymers, through the self-assembly of the corresponding mercapto-modified monomers promoted by the addition of a Ag^I salt.

Keywords: supramolecular hydrogels; self-assembly; silver; thiolates.

The ability to form hydrogels is not limited to polymers. There are also some small molecules which self-assemble into a three-dimensional (3D) network of fibres. These fibres form a gel in which the gelator molecules are solely held together by non-covalent interactions. These are known as supramolecular hydrogels or low molecular weight hydrogels,¹ and are emerging as an alternative to conventional polymer-based hydrogels. **Recently, the use of metal-ligand interactions has been shown to be a viable method for the construction of the so-**

* Corresponding author. E-mail: iodriozola@cidetec.es


1
2
3 called metallogels or metallo-supramolecular gels,² although the method has been
4
5 fundamentally used for the fabrication of organogels rather than hydrogels.
6
7

8 In a previous work we demonstrated that a supramolecular hydrogel can be formed
9
10 through the self-assembly of coinage metal glutathione thiolates.³ Here we show that
11
12 the method is not limited to the use of glutathione, by demonstrating that
13
14 supramolecular hydrogels can also be obtained by using smaller hydrophilic thiols.
15
16

17 The aim of the present work was to study the following hypothesis: is it possible
18
19 to create a supramolecular analogue of a conventional polymer through the self-
20
21 assembly of a structurally similar monomer? If so, would this analogue then present
22
23 similar gelling properties?
24
25

26 It is well known that several chemically cross-linked polymers and copolymers of *N*-
27
28 alkyl substituted acrylamides form temperature-sensitive hydrogels and their use in
29
30 biomedical applications is extensive.⁴ These polymers can be synthesised from the
31
32 corresponding *N*-alkylacrylamide monomers by anionic or free-radical polymerisation
33
34 using the appropriate initiator.⁵ Here the hydrophilic amide groups are covalently bound
35
36 to the polymer backbone. Thus, inspired by PDMA (**2**), a thiol group was attached to
37
38 the acrylamide monomer **1** (Scheme 1) to give amide **3**. The addition of AgNO₃ to **3** in
39
40 water results in the formation of the corresponding thiolate, with a molecular formula of
41
42 Ag–S–CH₂CH₂CON(CH₃)₂ (Equation 1). This compound self-assembles into the
43
44 supramolecular polymer **4** which subsequently gives a hydrogel. This species consists
45
46 of a Ag–S backbone from which *N,N*-dimethylamide groups are appended
47
48 perpendicularly.⁶
49
50



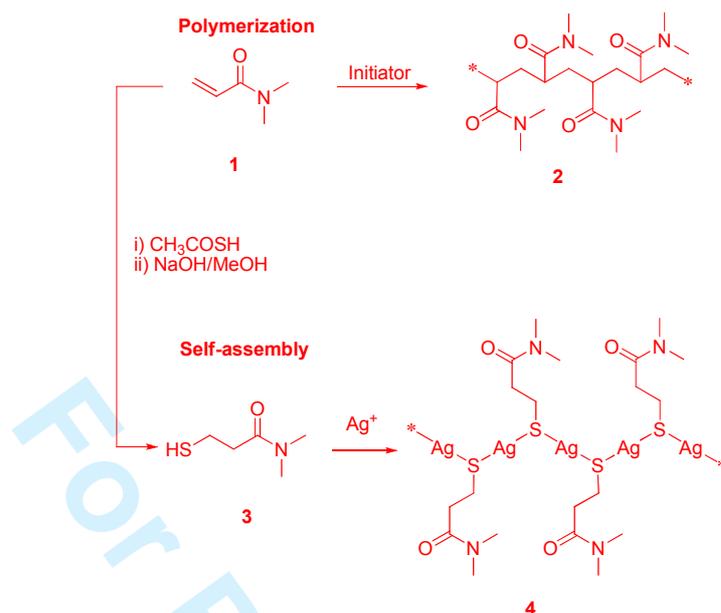


Scheme 1. Structural analogy of poly(*N,N*-dimethylacrylamide) **2** prepared from *N,N*-dimethylacrylamide **1**, and self-assembled thiolate **4** prepared from *N,N*-dimethyl-3-mercaptopropanamide **3** and AgNO₃.

The material was freeze-dried and analysed by IR spectrophotometry. The main feature of this spectrum is the absence of the S–H stretching band which appears at 2539 cm⁻¹ for **3** (see supplementary online material). EDS semiquantitative elemental analysis was consistent with a Ag–S–CH₂CH₂CON(CH₃)₂ molecular formula, showing a 1:1 sulfur/silver ratio.

Thiolate **4** is able to form a gel at concentrations as low as 0.5% w/v and the resulting hydrogel is stable for several months at room temperature. The gel shows a thermoresponsive behaviour, which is typical for supramolecular hydrogels.¹ When heated above the gel melting temperature (T_{gel}) the system behaves as a clear solution and a gel is formed again when allowed to cool (Scheme 2). The thermal stability of the hydrogel at different gelator concentrations (0.5 – 2% w/v) was studied. Figure 1 shows that within this concentration range the T_{gel} of the

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

supramolecular hydrogel is well expressed by a linear function of the thiolate concentration. Thus, T_{gel} was found to increase with the temperature, in concurrence with the literature for other supramolecular hydrogels.⁷

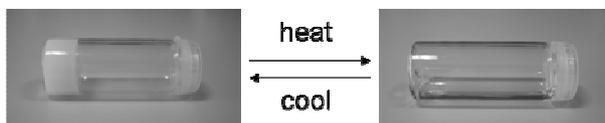

Scheme 2 Thermoreversible sol/gel transition of hydrogel **4** (1% w/v).

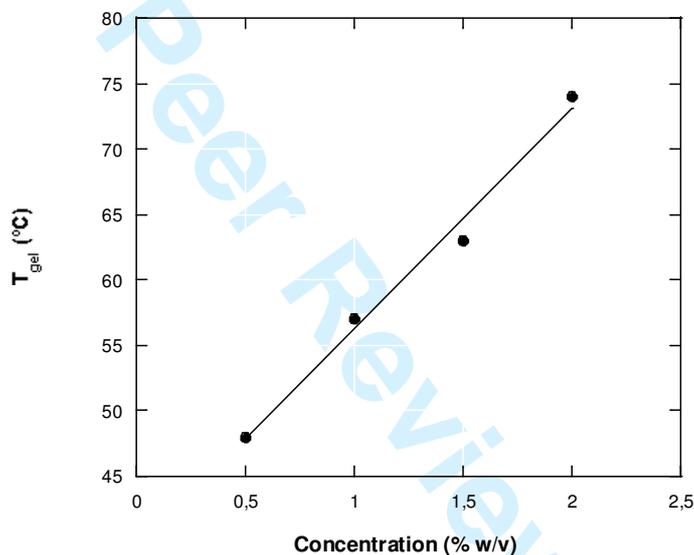


Figure 1. Variation of T_{gel} with the concentration of hydrogelator **4**.

SEM analysis of the freeze-dried hydrogel reveals a porous 3D network in form of fibres (Fig. 2a). TEM shows that the fibres themselves are composed of a granular pattern rather than being continuous (Fig. 2b-c).⁸ A close-up view of an individual fibre (Fig. 2d) reveals that the pattern consists of dark contrasted and irregular shaped granules adhered by an uncontrasted (soft matter) matrix. The granules are about 3.5 – 5 nm in diameter, and would correspond to oligomeric species of **4**. The width of the soft matrix is generally found to be at least 0.6 nm in size and can often reach up to 1.5 nm, but rarely above. Taking into account that the matrix is not contrasted in the TEM and that its width matches at least the size of amide **3** while

usually staying within the length of two elongated molecules, it is assumed that the amide chains act as the glue for the aggregation of the oligomeric silver thiolate granules through Van der Waals and hydrophobic forces. Thus, the phase transition of the hydrogel when heated above T_{gel} is thought to occur as a result of the disaggregation of these oligomeric granules, which are then stable and soluble in water. However, further investigation will be needed in order to fully understand the detailed structure of this oligomeric system and the interactions between the amide chains that take part in this thermoreversible process.

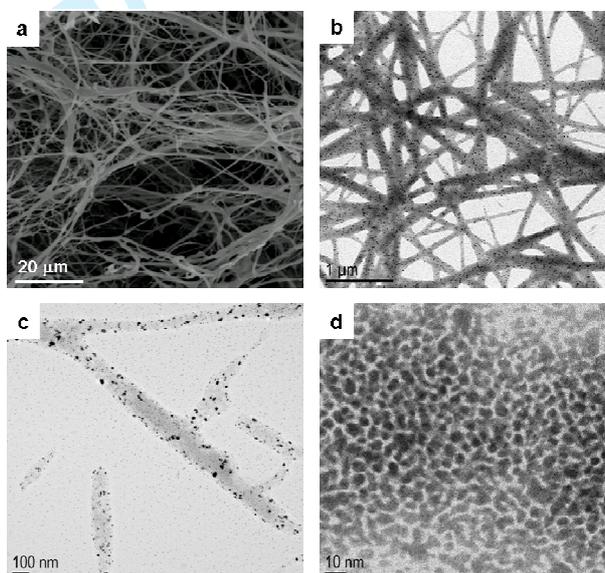


Figure 2. SEM (a) and TEM (b), (c) and (d) micrographs of the freeze-dried hydrogel.

In conclusion, a mercapto-modified acrylamide monomer has been used for the fabrication of a supramolecular polymer that forms a thermoreversible hydrogel. This demonstrates the possibility of designing supramolecular hydrogels, inspired by conventional polymers, through the self-assembly of the corresponding mercapto-modified monomers promoted by the addition of a Ag^{I} salt. The fact that the self-assembly occurs after the addition of the second component⁹ makes the system ideal for applications that require *in situ* gel formation.¹⁰

Acknowledgements: This work has been financially supported by Eusko Jaurlaritza/Gobierno Vasco through an ETORTEK grant.

Notes and references

1. (a) de Loos, M.; Feringa, B. L.; van Esch, J. H. *Eur. J. Org. Chem.* **2005**, *17*, 3615-3631. (b) Estroff, L. A.; Hamilton, A. D. *Chem. Rev.* **2004**, *104*, 1201-1217. (c) Sangeetha, N. M.; Maitra, U. *Chem. Soc. Rev.* **2005**, *34*, 821-836.
2. See for example: (a) Xing, B.; Choi M.; Xu, B. *Chem. Commun.* **2002**, 362-363. (b) Xing, B.; Choi M.; Xu, B. *Chem. Eur. J.* **2002**, *8*, 5028-5032. (c) Beck, J. B.; Rowan, S. J. *J. Am. Chem. Soc.* **2003**, *125*, 13922-13923. (d) Wei, Q.; James S.L. *Chem. Commun.* **2005**, 1555-1556. (e) Kishimura, A.; Yamashita, T.; Aida, T. *J. Am. Chem. Soc.* **2005**, *127*, 179-183.
3. (a) Odriozola, I.; Loinaz, I.; Pomposo, J. A.; Grande, H. J. *J. Mater. Chem.* **2007**, *17*, 4843-4845. (b) Odriozola I.; Ormategui N.; Loinaz I.; Pomposo J. A.; Grande H. J. *Macromol. Symp.* **2008**, *266*, 96-100.
4. (a) Jeong, B.; Kim, S. W.; Bae, Y. H. *Adv. Drug Delivery Rev.* **2002**, *54*, 37-51. (b) Qiu, Y.; Park, K. *Adv. Drug Delivery Rev.* **2001**, *53*, 321-339. (c) Bromberg, L. E.; Ron, E. S. *Adv. Drug Delivery Rev.* **1998**, *31*, 197-221. (d) Schild, H. G. *Prog. Polym. Sci.*, **1992**, *17*, 163-249.
5. For the synthesis of PDMA, see for example: Xie, X.; Hogen-Esch, T. E. *Macromolecules* **1996**, *29*, 1746-1752 and references cited therein.
6. For a more detailed description of the structure of polymeric silver thiolates, see: (a) Bensebaa, F.; Ellis, T. H.; Kruus, E.; Voicu, R.; Zhou, Y. *Can. J. Chem.* **1998**, *76*, 1654-1659. (b) Bensebaa, F.; Ellis, T. H.; Kruus, E.; Voicu, R.; Zhou, Y. *Langmuir* **1998**, *14*, 6579-6587. (c) Dance, I. G.; Fisher, K. J.; Banda, R. M. H.; Scudder, M. L. *Inorg. Chem.* **1991**, *30*, 183-187. (d) Parikh, A. N.; Gillmor, S. D.; Beers, J. D.; Beardmore, K. M.; Cutts, R. W.; Swanson, B. I. *J. Phys. Chem B* **1999**, *103*, 2850-2861.
7. See for example: (a) Menger, F. M.; Caran, K. L. *J. Am. Chem. Soc.* **2000**, *122*, 11679-11691. (b) Roy, S.; Dasgupta, A.; Das, P. K. *Langmuir* **2007**, *23*, 11769-11776. (c) Saha, A.; Manna, S.; Nandi, A. K. *Langmuir* **2007**, *23*, 13126-13135. (d) Shome, A.; Debnath, S.; Das, P. K. *Langmuir* **2008**, *24*, 4280-4288.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
8. The specimens for TEM analysis were not stained. The larger (20–30 nm) and very dark spots present on the fibres correspond to elemental Ag nanoparticles (as confirmed by EDS), coming from the reduction of part of the Ag⁺ during the formation of **4**, where the thiol acts as the reducing agent. These nanoparticles are also formed during the TEM analysis, by reduction with the electron beam. See for example: Kim, J. U.; Cha, S. H.; Shin, K.; Jho, J. Y.; Lee, J. C. *J. Am. Chem. Soc.* **2005**, *127*, 9962-9963.
9. For a recent review on two-component gels, see: Hirst, A. R.; Smith, D. K. *Chem. Eur. J.* **2005**, *11*, 5496-5508.
10. (a) Ruel-Gariepy, E.; Leroux, J. C. *Eur. J. Pharm. Biopharm.* **2004**, *58*, 409-426. (b) Van Tomme, S. R.; Storm, G.; Hennink, W. E. *Int. J. Pharm.* **2008**, *355*, 1-18.

Supplementary online material for


A Thermoreversible Supramolecular Hydrogel Inspired by Poly(*N,N*-dimethylacrylamide)

Pablo Casuso,^a Iraida Loinaz,^a Marco Möller,^b Pedro Carrasco,^a José A. Pomposo,^a
Hans J. Grande^a and Ibon Odriozola*^a

^aCIDETEC Centre for Electrochemical Technologies, New Materials Department, Parque Tecnológico de San Sebastián, Paseo Miramón 196, 20009 Donostia-San Sebastián, Spain; ^bCIC biomaGUNE, Parque Tecnológico de San Sebastián, Paseo Miramón 182, 20009 Donostia-San Sebastián, Spain

* To whom correspondence should be addressed. E-mail: iodriozola@cidetec.es

Synthesis of *N,N*-dimethyl-3-mercaptopropanamide (**3**)

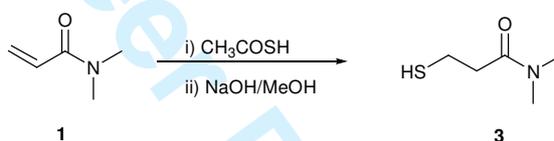

Thioacetic acid (2.1 mL, 30 mmol) was added drop wise to *N,N*-dimethylacrylamide (3.1 mL, 30 mmol) cooled at 0 °C under nitrogen. After the mixture was stirred at room temperature for 4 hours, MeOH (15 mL) was added and the solution was cooled to 0 °C. Then aqueous NaOH 3N (15 mL) was added and the reaction stirred at room temperature for 2 hours. The mixture was neutralized to pH ~ 7 by addition of concentrated HCl, and concentrated *in vacuo* to remove methanol. The aqueous concentrate was extracted with CH₂Cl₂ (3 x 30 mL). The organic extract was washed with brine, dried over magnesium sulfate, filtered, and concentrated *in vacuo* to give **3**. The crude material was purified by distillation at high vacuum. Yield: 3.62 g, 91% (colorless oil). ¹H NMR (500 MHz, CDCl₃) δ (ppm) = 2.98 (s, 3H), 2.94 (s, 3H), 2.81-2.77 (m, 2H), 2.63 (t, *J* = 7 Hz, 2H), 1.75 (t, *J* = 8 Hz, 1H). ¹³C NMR (126 MHz, CDCl₃) δ (ppm) = 170.6, 37.2, 36.9, 35.3, 20.0.

Synthesis of the hydrogel (**4**)

For the preparation of a 1% w/v hydrogel: AgNO₃ 1N (2 mL) is added to a solution of **3** (28 mg, 2 mmol) in H₂O (3 mL) and allowed to stand. After a few minutes a yellowish gel is formed. ¹H NMR (500 MHz, H₂O/D₂O) δ (ppm) = 3.27 (t, *J* = 6 Hz, 2H), 3.05 (s, 3H),

2.96 (t, $J = 6$ Hz, 2H), 2.94 (s, 3H).

SEM and TEM sample preparation

SEM was recorded on a JEOL JSM5610-LV apparatus. The specimen was prepared by placing a frozen sample of the hydrogel in the sputter coating chamber at high vacuum for 1 hour, after which a thin layer of gold was applied.

TEM specimen was prepared by adding a drop of hot hydrogel (sol) onto a carbon-coated copper grid. Images were recorded on a JEOL JEM-2100F UHR apparatus operated at 200 kV.

Energy dispersive X-ray spectroscopy (EDS)

Analysis was performed on an INCA-300 model from OXFORD.

a) Polymer 4

All results in atomic percent:


| | C | N | O | S | Ag | Total |
|--------|-------|-------|-------|------|------|--------|
| zone 1 | 23.90 | 31.17 | 35.04 | 5.22 | 4.68 | 100.00 |
| zone 2 | 23.05 | 30.77 | 31.95 | 7.07 | 7.16 | 100.00 |
| zone 3 | 23.24 | 33.02 | 33.46 | 5.29 | 4.99 | 100.00 |

| | C | N | O | S | Ag |
|------|-------|-------|-------|------|------|
| Max. | 23.90 | 33.02 | 35.04 | 7.07 | 7.16 |
| Min. | 23.05 | 30.77 | 31.95 | 5.22 | 4.68 |

All results in weight percent:


| | C | N | O | S | Ag | Total |
|--------|-------|-------|-------|-------|-------|--------|
| zone 1 | 14.68 | 22.32 | 28.66 | 8.55 | 25.79 | 100.00 |
| zone 2 | 12.48 | 19.43 | 23.04 | 10.21 | 34.84 | 100.00 |
| zone 3 | 14.06 | 23.30 | 26.97 | 8.54 | 27.12 | 100.00 |



| | C | N | O | S | Ag |
|------|-------|-------|-------|-------|-------|
| Max. | 14.68 | 23.30 | 28.66 | 10.21 | 34.84 |
| Min. | 12.48 | 19.43 | 23.04 | 8.54 | 25.79 |

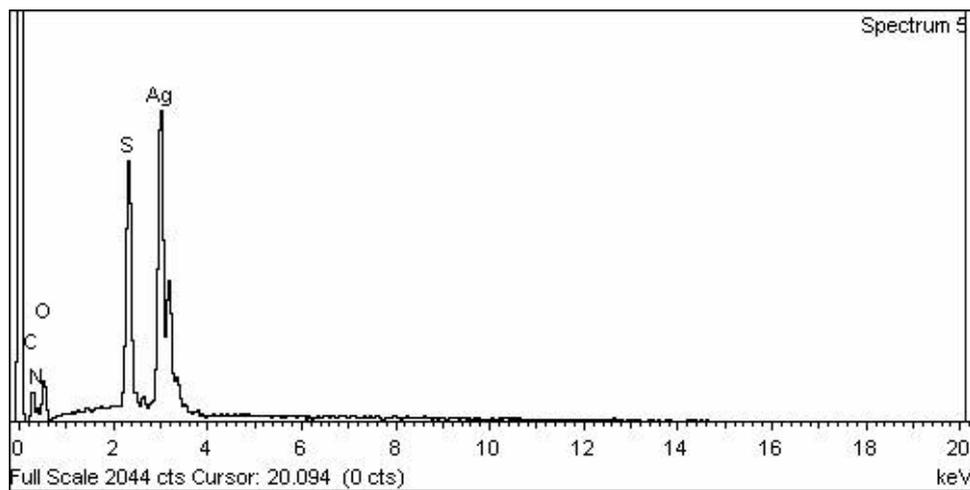



21
22
23
24


NMR Spectra

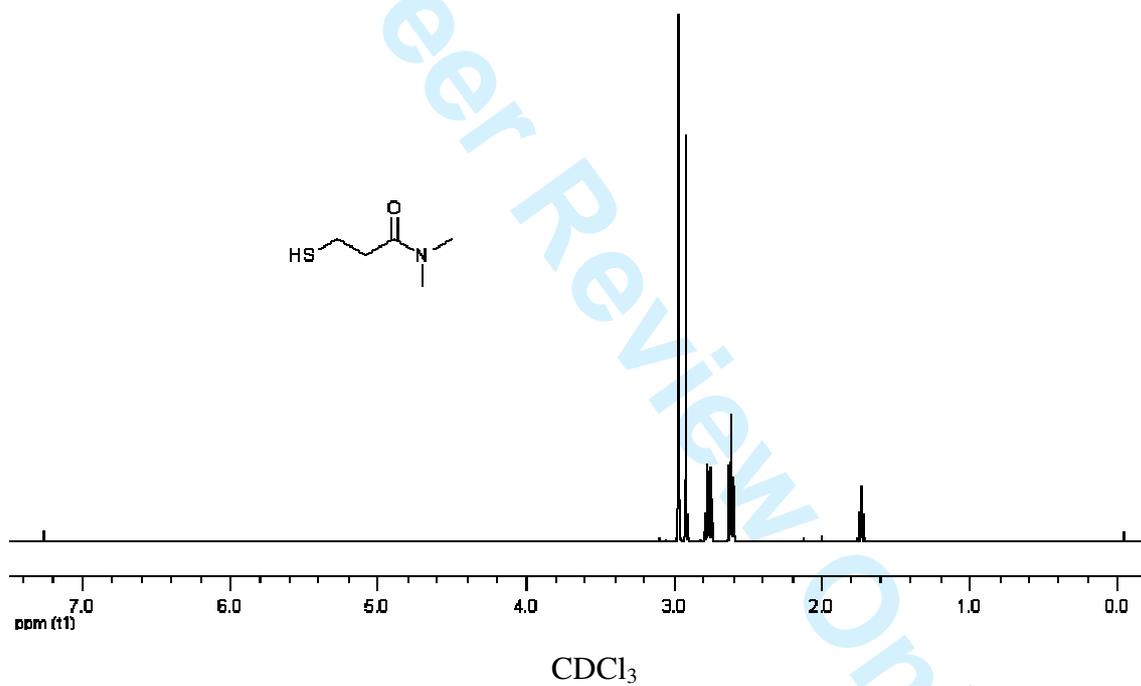

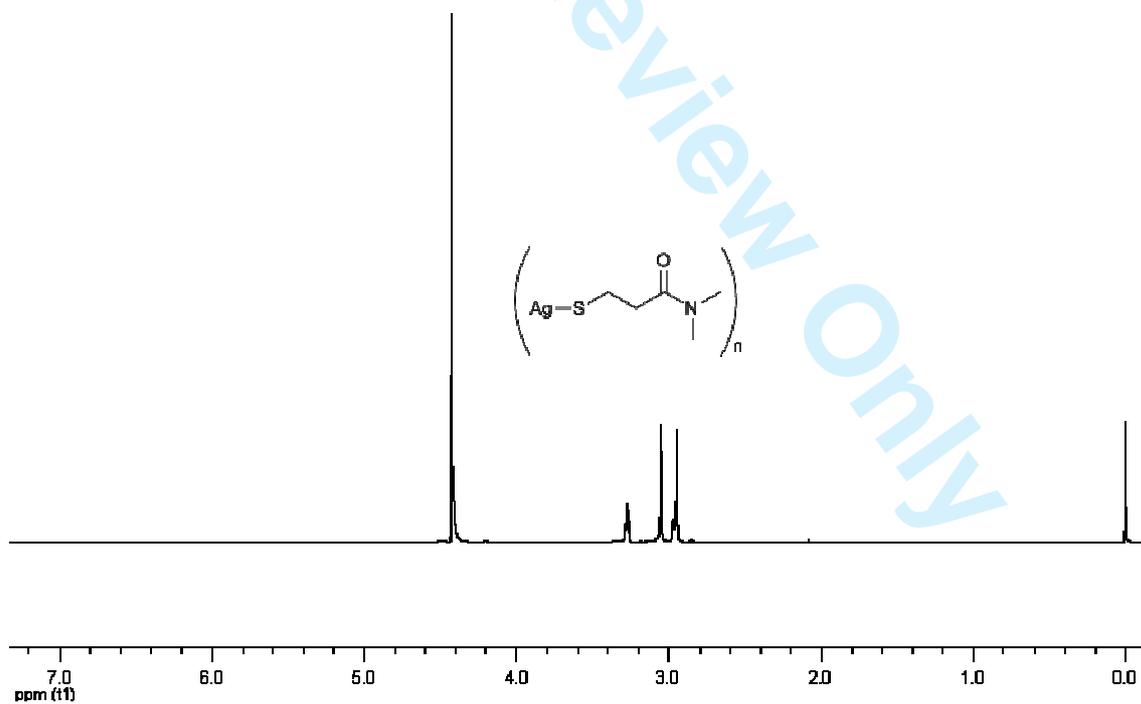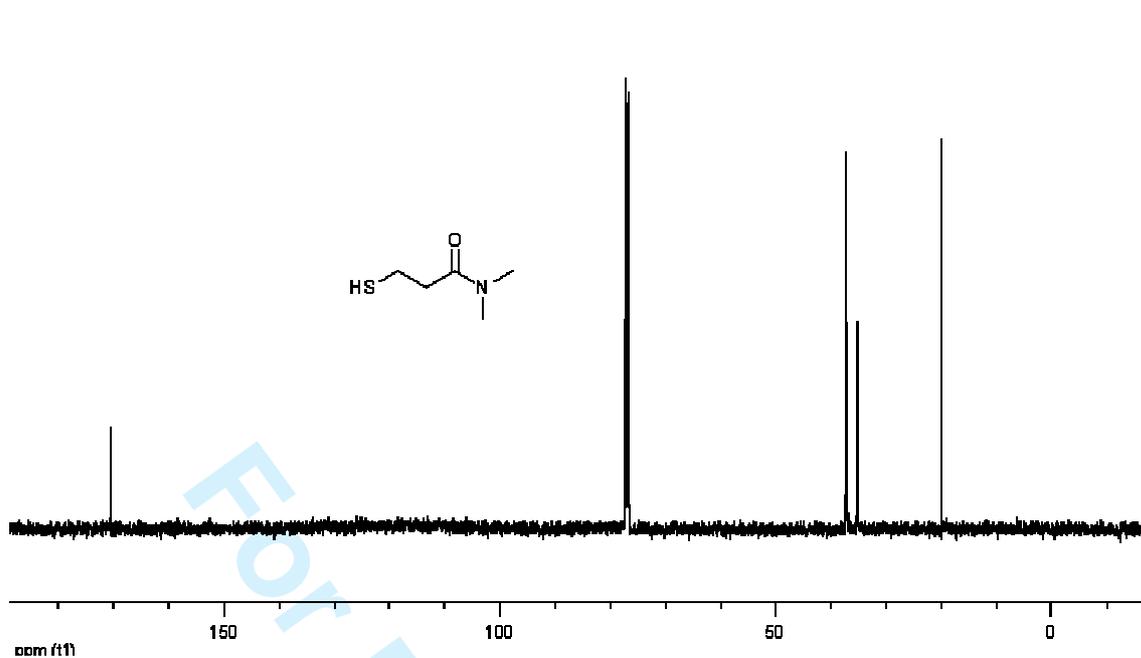

IR Spectra

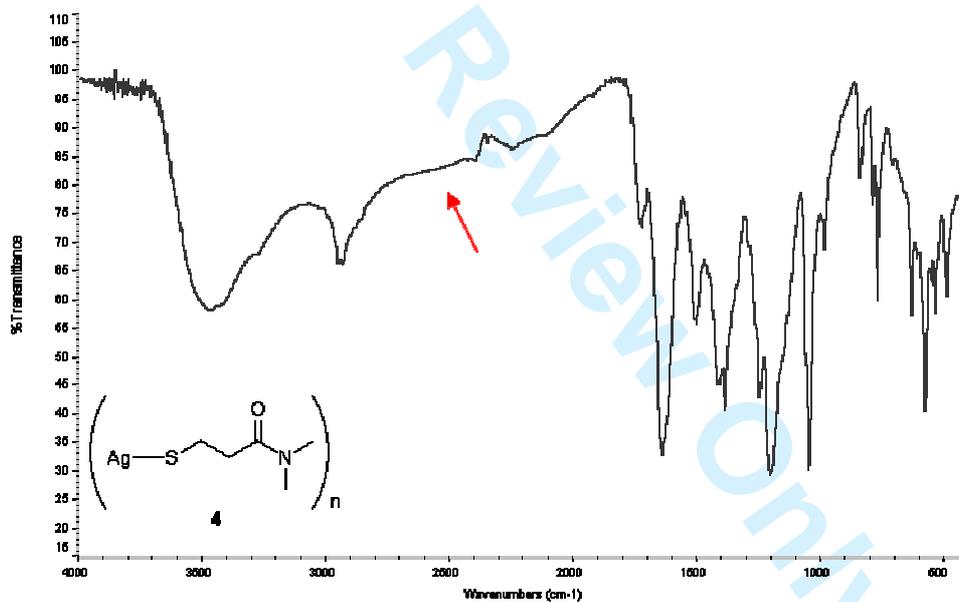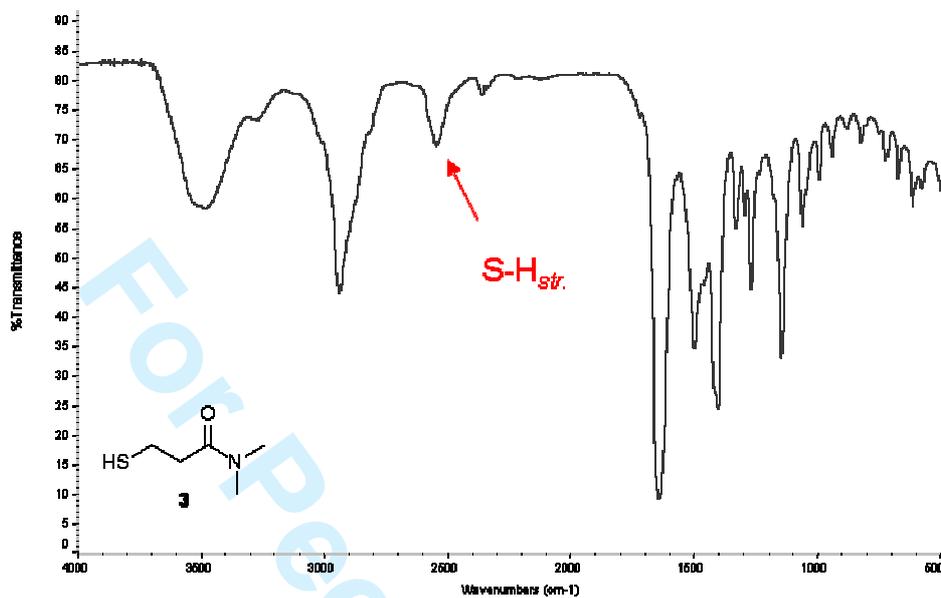


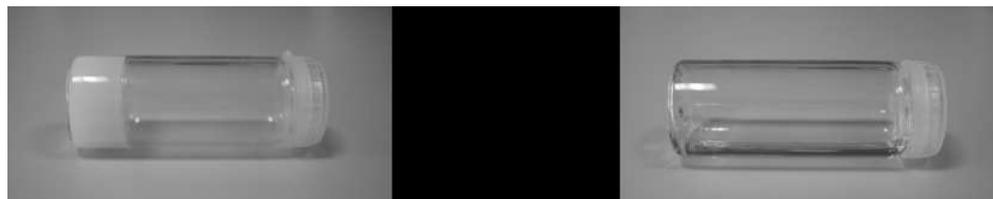

140x27mm (150 x 150 DPI)


or Peer Review Only

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

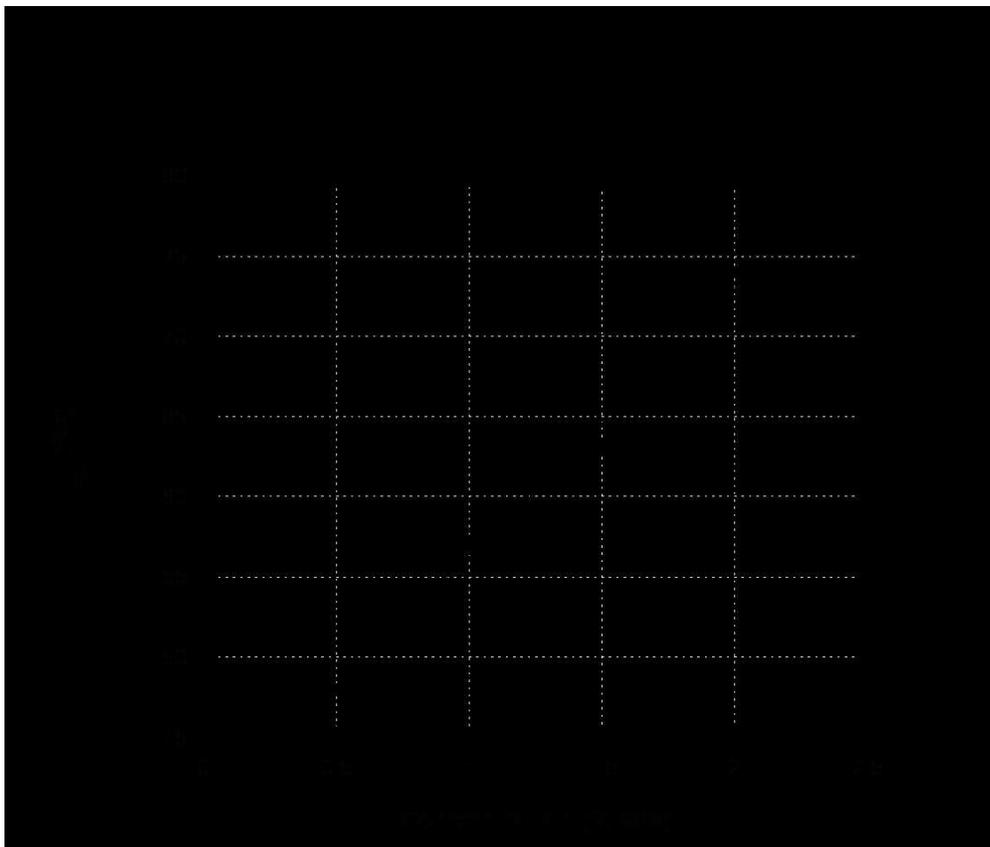

190x161mm (150 x 150 DPI)

View Only

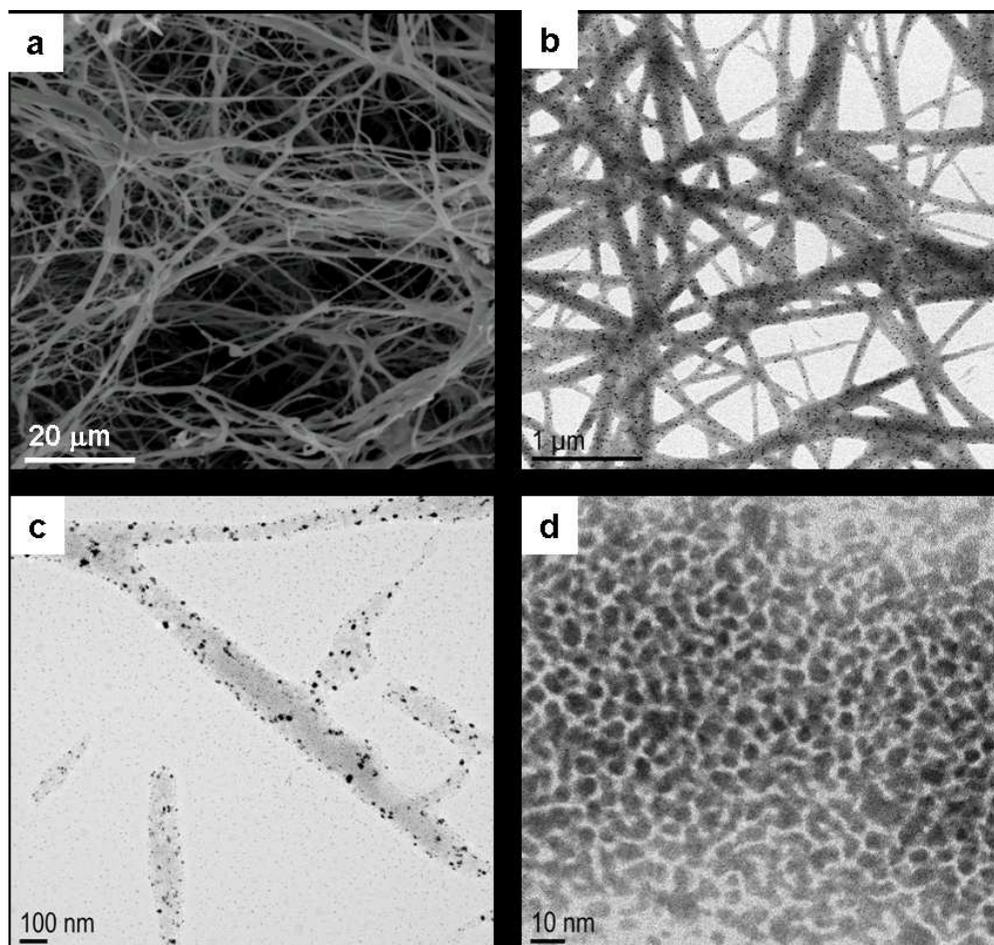

144x136mm (150 x 150 DPI)

Only