



**HAL**  
open science

## Heterogeneities in amorphous systems under shear

J.-L. Barrat, Anael Lemaitre

► **To cite this version:**

J.-L. Barrat, Anael Lemaitre. Heterogeneities in amorphous systems under shear. 2010. hal-00521816v2

**HAL Id: hal-00521816**

**<https://hal.science/hal-00521816v2>**

Preprint submitted on 25 Jan 2011 (v2), last revised 29 Jan 2011 (v3)

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Heterogeneities in amorphous systems under shear

Jean-Louis Barrat

*Université de Lyon; Univ. Lyon I, Laboratoire de Physique de la Matière Condensée et des Nanostructures; CNRS, UMR 5586, 43 Bvd. du 11 Nov. 1918, 69622 Villeurbanne Cedex, France*

Anaël Lemaître

*Université Paris-Est – Navier – CNRS UMR 8205 – ENPC – LCPC  
2 allée Képler, 77420 Champs-sur-Marne, France*

**OXFORD**  
UNIVERSITY PRESS



# Abstract

The last decade has seen major progresses in studies of elementary mechanisms of deformation in amorphous materials. Here, we start with a review of physically-based theories of plasticity, going back to the identification of “shear-transformations” as early as the 70’s. We show how constructive criticism of the theoretical models permits to formulate questions concerning the role of structural disorder, mechanical noise, and long-ranged elastic interactions. These questions provide the necessary context to understand what has motivated recent numerical studies. We then summarize their results, show why they had to focus on athermal systems, and point out the outstanding questions.

## 0.1 Introduction

Rheology and plasticity, although they both investigate the flow of solid materials, are generally considered as two separate fields of materials science. Plasticity deals with the deformation of “hard” solids, characterized by large elastic moduli (typically in the GPa range). Rheology, on the other hand, deals with much softer materials, such as colloidal pastes, foams, or other “complex fluids” (Larson, 1999) with moduli that can vary from a few Pa to kPa. In view of these differences, the experimental tools used to investigate the flow of hard and soft materials are widely different, whether they are mechanical or involve more indirect microscopic characterizations.

Still, if one temporarily forgets about the differences in the scale of stress levels, striking similarities appear in the behavior of these different materials, as illustrated schematically in figure 0.1. The differences in stress scales are indeed easily understood in terms of the interactions. The scale for elastic moduli is an energy per unit volume. In hard materials, typical energies will be in the range 0.1-1eV, and the typical length scales are of order of nanometers, or even smaller. In softer materials, the energy scale is often comparable to  $k_B T$ , and length scales of the order of a tenth of a micron. Finally, the case of foams corresponds to a stress scale set by the surface tension  $\gamma$  divided by the typical bubble size. It is not excluded, that common physical properties can be found in such widely different systems, if the proper elementary units are considered and the appropriate rescaling are made.

In terms of “reduced” parameters, however, the experimental conditions may correspond to very different ranges for the various systems investigated. For example, a foam or a two dimensional “bubble raft” is essentially always athermal (the thermal fluctuations are irrelevant compared to the energies involved at the scale of individual bubbles) so that it should be compared to metallic or polymer glasses at low temperatures. On the other hand, a not too dense colloidal system at room temperature, in which thermal fluctuations are significant, could be compared to systems close to their glass transition temperature. The same type of considerations applies to time

scales and their comparison with the applied deformation rates, which have a strong influence on the stress-strain curve, as sketched in figure 0.1. Typically, the stress peak  $\sigma_{max}$  shown in this figure tends to display a logarithmic increase with the deformation rate  $\dot{\epsilon}$  and, when ageing is observed, with the age  $t_w$  of the system.

In this chapter, we will limit our considerations to noncrystalline, amorphous materials. In crystalline materials, flow can be described in terms of dislocation motion, and although the interaction between these extended defects may lead to a macroscopic behavior similar to that of amorphous materials (Miguel and Zapperi, 2006), the underlying microscopic physics is different. For amorphous materials it will be shown that flow defects, if they exist, are localized rather than extended. We will also exclude from our considerations the case of real granular materials, that raise several complications such as the importance of gravity and that of friction. However, we will mention some simulation works that are dealing with idealized, frictionless grains in the absence of gravity.

Why is a chapter on sheared materials included in a book on dynamical heterogeneities ? The standard plasticity or rheology approach is based on macroscopic constitutive equations, established using symmetry arguments (Lubliner, 2008). These equations relate the stress and strain (or strain history) in the system, within a fully homogeneous, continuous medium description. However, the notion of dynamical heterogeneities naturally emerges when one attempts to reach an understanding of the microscopic mechanisms that underly the macroscopic behavior. Is it possible to identify microscopic heterogeneities, that would in some respects play the role assigned to dislocations in the flow of crystalline materials ? What governs the dynamical activity of such heterogeneities, what are their interactions and correlations, and do they organize on larger scales? From the pioneering experiments of Argon (Argon and Kuo, 1979) emerged the notion of "shear transformation zones", a localized (in space and time) region of material in which the plastic activity takes place (Argon, 1982). Such local yield events have been very clearly identified in experiments on bubble rafts, in colloidal systems (Schall *et al.*, 2007), as well as in various atomistic simulations of low temperature deformation (see e.g. (Falk and Langer, 1998, Maloney and Lemaitre, 2006, Tanguy *et al.*, 2006)). They are now believed to constitute the elementary constituent of plastic deformation in amorphous solids at low temperature. However, their cooperative organisation is far from being understood, although a number of models based of this notion of elementary event have been developed and studied analytically at the mean field level or numerically. The discussion of these microscopic, dynamical heterogeneities will be the core of this chapter.

Another, very different aspect that escapes the purely macroscopic description of flow is the frequent experimental observation that strain in solid materials can take place in a very heterogeneous manner at the macroscopic level. This phenomenon, described as the existence of "shear bands" or "strain localisation", takes place both in hard and soft materials, under various conditions of deformation. Instead of being evenly distributed and uniform through the system (affine deformation), the deformation is concentrated inside a localized region of space, typically a two dimensional "shear band" with a finite thickness. Within such shear bands that concentrate the whole macroscopic deformation, the local strain becomes very large in a short time,

eventually leading to material failure for hard materials. In soft materials, that, in contrast to hard materials, can sustain steady flow when strained in a pure shear (Couette) geometry, shear bands can become permanent features of the steady state flow and coexist with immobile parts of the same material. While shear bands are clearly macroscopic features of the flow, understanding the mechanism of their formation and stability necessitates the introduction of auxiliary state variables and associated length scales, which in turn could be related to the existence of flow heterogeneities at smaller scales. These aspects will be discussed further in section 1.2.7.

We mention to close this introduction that the focus of our paper will be on simple shear deformation. In most materials, it is expected that the study of such deformations will allow one to unveil the mechanisms of plasticity in more complex situations, as the plastic deformation proceeds with little or no densification. This is true in metallic glasses or soft condensed system, where plastic deformation often takes place at almost constant volume, but less in network materials with a lower Poisson ratio, where densification and shear deformation are observed simultaneously (Rouxel *et al.*, 2008).


## 0.2 Theoretical background

### 0.2.1 Macroscale

**Plasticity at the macroscale.** Many tests have been developed to characterize plastic behavior. They involve deforming a piece of material under various conditions: constant stress, constant or oscillatory strain-rate, step stress or strain,... while measuring the response using appropriate observables. Typical stress responses, for a material loaded at constant strain-rate, are depicted in Figure 0.1. When the strain is vanishingly small, the material responds elastically. As strain increases, plasticity progressively sets in and the stress smoothly rounds off. This transient response obviously depends on the evolution of the internal state of the system during loading, hence on sample preparation and loading rate. Further increase of strain may be accompanied, in some circumstances, with the onset of an instability, as deformation localizes along shear bands and leads the material to failure. When this instability can be avoided, however, stress reaches a steady state plateau value.

In general, it is difficult experimentally to achieve situations in which the flow is truly uniform: external driving must always be applied at boundaries, so that material flow must be inhomogeneous to adapt to these conditions (a exception is the flow of a Newtonian fluid in plane Couette geometry). So, real material flows are always inhomogeneous, and one often speaks of “localization” in this context, even to describe a steady state flow. This acception of “localization” is most often found in rheology, as typical experimental set-ups, such as the Couette cell necessarily lead to flow profiles which are inhomogeneous (Coussot, 2005). “Localization” is also used in another context, for example, in experiments on “hard” glasses (Schuh *et al.*, 2007), when it refers to an instability which is not directly associated with the macroscopic stress inhomogeneity and can only be observed during transient as it leads to failure. Whether these two forms of localization are related remains an open questions.

**Constitutive equations.** One goal of theories of plasticity is to provide a macroscopic description of the deforming medium, analogous to the Navier-Stokes equations

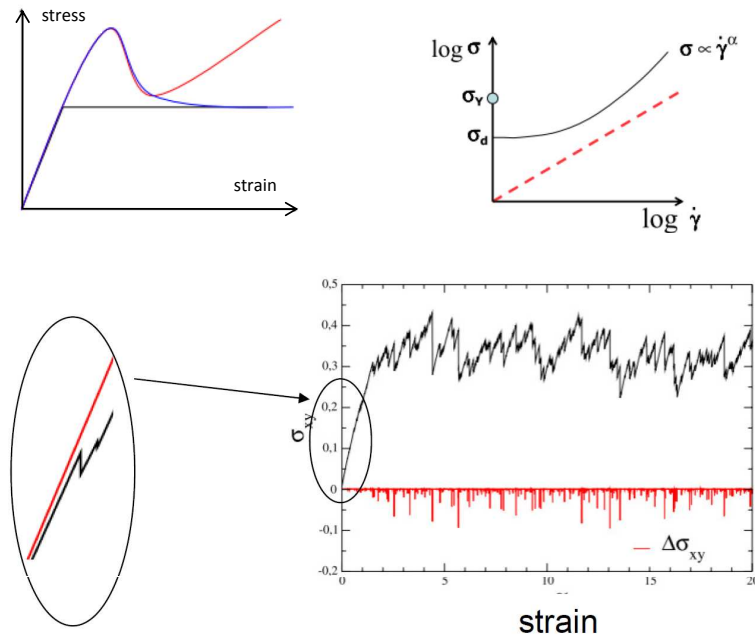

**Fig. 0.1** Top left: schematic illustration of a stress strain curve for the plastic deformation of a solid material. The three curves correspond respectively to ideal elastoplastic behavior, a metallic and a polymeric system at finite strain rate. The strain hardening part at large strain is specific of polymer systems. Top right: schematic illustration of a flow curve for a soft material; the dotted line is the Newtonian fluid case, the low strain rate limit of the full curve corresponds to the yield stress. Bottom: actual response of a simulated strained glass at low temperature. Note the large stress fluctuations, that are associated with the finite size of the sample. The stress variations are also shown. The zoom on the elastic part at low strain shows that small plastic events are also observed in this part. Adapted from (Tanguy *et al.*, 2006)

for Newtonian fluids. As illustrated in Figure 0.1, plastic materials exhibit significant, preparation or age-dependent, transients in which stress does not match its steady state value. Proper account of either transient response or of instabilities of the steady inhomogeneous flow must rely on a description of how the internal state of the system depends on loading history. This entails identifying variables to properly characterize the material state and providing constitutive equations to complement the relevant conservation equations (momentum, but also possibly density or energy). The search of constitutive equations often rests on the idea that it is possible to provide a local and instantaneous representation of the material state, that is to describe its response in terms of relations between local quantities (such as stresses, strains, energy, density,...) and their derivatives.

The introduction of internal state variables is also a necessity if one wants to study localization, or instabilities in the material response. For example, it was shown

that constitutive equations which are approximated (grossly) by their steady state stress/strain-rate relation lead to instability criteria which are rudimentary, and that internal variables have to be introduced to capture couplings of the material response with other degrees of freedom such as elasticity (Rice and Ruina, 1983). Situations when the plastic response is unsteady play a critical role in the identification of relevant state variables. Localization thus attracts a considerable amount of interest not only for its practical importance, but also for the theoretical implications of identifying the proper variables governing its development.

**State variables for localization.** One most obvious state variable is temperature. Clearly, it is expected to increase due to plastic activity when a material is strained under adiabatic conditions. Its role in localization has thus been the subject of a long-standing debate in the metallic glass community (Schuh *et al.*, 2007). Some defend that localization could be due to local heating and should be treated by introducing thermal dependence in the stress/strain rate relationship, plus energy conservation equations. The consensus, however, now is that this argument fails because the dissipated energy due to plasticity is evacuated too fast (Schuh *et al.*, 2007). Other features of material response, such as localization or the peak stress, depend sensitively on age at time scales which are completely separated from those of thermal exchanges. These observations rule out the role of thermal inhomogeneities in most cases.

A model proposed recently to account for shear banding or fracture focusses on compressibility and density fluctuations (Furukawa and Tanaka, 2006). Like the thermal theories of localization, it is based on a purely macroscopic description. It assumes that (i) the flow is Newtonian and (ii) stresses always assume their steady-state values. The values of shear stress and pressure are thus provided by simple steady state equations, function of strain-rate and density, and localisation is in a sense a kinematic effect. The proposed scenario involves a strong density dependence of the viscosity on density or pressure. As a result, a density fluctuation (which is usually neglected in the description of incompressible flows) results in a local decrease of the viscosity, which in turn increases the local shear rate and an amplification of the fluctuation. A linear stability analysis of the Navier Stokes equation under these conditions shows that for shear rates larger than  $(\partial\eta/\partial P)^{-1}$ , large wavelength density fluctuations at 45 degrees from the flow direction become linearly unstable. This leads to amplification of density fluctuations and potentially to material failure.

Similar arguments have been used to describe the coupling between density fluctuations and rheology in polymer solutions (Helfand and Fredrickson, 1989) This type of scenario predicts that strain localisation only operates *above* a critical strain rate, whereas experiments on metallic glasses clearly show that localization, in the low temperature regime is a phenomenon which occurs when the strain rate lies below a critical value (Schuh *et al.*, 2007). It thus seems that the localization they would predict is different from the phenomenon which is discussed in metallic glasses at low strain rates.

**Discussion.** These difficulties emphasize usefully the problems met when formulating theories of plasticity. It seems unlikely that a description involving only the usual thermo-mechanical observables (stress, pressure, temperature) can be sufficient.



We know indeed that these variables do not provide a complete representation of the internal structure of glasses, the dynamics of which, even in the absence of stress, involves hopping in potential energy landscape (PEL) (Stillinger, 1995, Debenedetti and Stillinger, 2001), over distributed energy barriers (Doliwa and Heuer, 2003*a*, Doliwa and Heuer, 2003*b*, Doliwa and Heuer, 2003*c*). Deformation complicates the picture as it competes with relaxation (Utz *et al.*, 2000) and constantly “rejuvenates” the glassy structure. The question is thus, using a few dynamical equations involving a limited set of state variables, to be able to describe the response of a glass driven out-of-equilibrium by external deformation. To describe the transient stress response upon loading, as exemplified in Fig. 0.1, we would also have to be able to describe the state of the glass which is produced by annealing in terms of variables that can be introduced in a description of plastic response.

The description of flow in amorphous solids that will be presented in the following is essentially based on ideas from elasticity theory, and therefore starts on the low temperature, solid side of the glass or jamming transition. We mention briefly here another alternative approach, the mode-coupling approach of Fuchs and Cates (Fuchs and Cates, 2002). Let us remind that the mode coupling approach to dense liquids involves a nonlinear feedback mechanism, in which the relaxation dynamics of a given density fluctuation at some wavevector  $\mathbf{k}$  is coupled to that of all other fluctuations at different wavevectors. This feedback leads to structural arrest – i.e. absence of relaxation and apparition of a frozen structure – at some finite density and temperature. The effect of shear described by Fuchs and Cates is the advection of density fluctuations, in such a way that the coupling that leads to this non linear feedback weakens with time, and that a relaxation eventually results. A dynamical yield stress is obtained as the zero shear rate limit of the stress under steady shear, which turns out to be non zero for high density, strongly coupled systems that the theory predicts to be in a nonergodic state at zero shear. The theory was elaborated by Brader and Fuchs (Brader *et al.*, 2008), and predicts rheological behavior that is in very reasonable agreement with experimental observations on colloidal glasses, together with a prediction of the deviation from equilibrium fluctuation-dissipation theorem. However, this mode coupling description has not been extended, up to now, to the description of dynamical heterogeneities.

### 0.2.2 Local Inelastic Transformations

In crystals, the mechanisms of plastic deformation involve the motion and generation of dislocations, which are a class of topological defects of the periodic structure. The possibility to identify and precisely define the objects responsible for irreversible deformation has played and continues to play a key role in formulating phenomenologies and constructing governing equations for crystalline plasticity. In contrast, the state of knowledge on amorphous systems lies far behind, because the elementary objects governing the plastic response remain quite difficult to pinpoint.

Most modern theories of plasticity are based on the idea, proposed by Ali Argon in the late 70’s (Argon, 1979), that macroscopic plastic deformation is the net result of an accumulation of local, collective, rearrangements of small volume elements—typically 5-10 particules in diameter. Initially corroborated by the observation of flow in a

bubble raft (Argon and Kuo, 1979), this idea is now firmly supported by numerical simulations (Argon *et al.*, 1995, Falk and Langer, 1998, Maloney and Lemaitre, 2004*b*, Maloney and Lemaitre, 2004*a*, Maloney and Lemaitre, 2006, Tanguy *et al.*, 2006), and by a recent experiment (Schall *et al.*, 2007).

In contrast with crystals, however, the notion of rearrangements (also called “local inelastic transformations”, “shear transformations”, or “(zone) flips”) refers to a process, not to a specific type of defect. Means have been devised to identify “zones” before they flip, via measurements of particule displacement fields, (Lemaitre and Caroli, 2007) or of local elastic moduli (Yoshimoto *et al.*, 2004, Tsamados *et al.*, 2009), but these observations can be unequivocally correlated with rearrangements only rather close to yielding, and there is no consensual prescription to identify *a priori* the locations (the “zones”) where flips occur. Of course, it seems reasonable to infer that there should be some specific features of the local packing, which make these transformations possible—and are probably related to the fluctuations of local thermodynamic quantities such as energy, stress, or density (free-volume). Many terms have been coined to reflect this notion—“flow defects”, “ $\tau$ -defects”, or more recently “shear transformation zones” (STZ)—but what is precisely a zone, how could they be identified before-the-fact, remain largely open questions.


This idea does not imply that only *shear* transformations exist, neither that each rearrangement is a pure shear event. Rearrangements may involve some local changes of volume too, and some theories—such as free-volume approaches—may attempt to take this into account. Occurring at a very local scale, rearrangements are also inevitably broadly distributed. But in view of constructing a theory of stress relaxation, it is the net effects of local contributions to shear strain which clearly matters.

### 0.2.3 Activation Theories

Activation theories attempt to describe plasticity as the net result of independent shear transformations, which are supposed to be rare events, the occurrence of which is controlled by thermal activation. It is thus assumed that the system spends most of its time near local equilibria: clearly, this picture belongs to a low temperature region, when the dynamics in PEL would be described by unfrequent hops between local minima. With these postulates, constitutive equations require a specification of transition rates (function of energy, density, stress) governing the rearrangements.

**Eyring’s theory.** The simplest form of such an activation theory of material flow dates back to the works by Eyring, and was initially intended to account for the viscous behavior of liquids (above  $T_g$ ). In Eyring’s view, flow proceeds by the motion of single molecules into holes left open by neighboring ones. This obviously misses the possibility that elementary events are in fact collective, but Eyring introduces several assumptions which are still quite fundamental to the field and useful to keep in mind as a reference.

He first assigns a typical value  $E$  to the energy barrier that must be overcome to allow such hops—it is, in his view, the energy needed to create a hole—and observes that various types of hops are possible, which can either increase or reduce the macroscopic stress. He then restricts his description to two types of opposite moves, contributing to

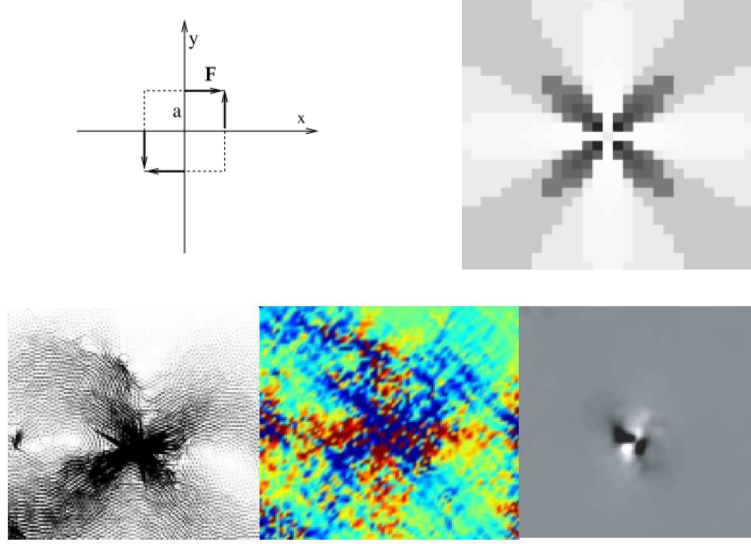

**Fig. 0.2** Top: schematic illustration of a force quadrupole that corresponds to the theoretical description of shear transformation zones (left), and its Eshelby stress field. Bottom, from left to right: displacement field, stress response, and energy change associated with a localized plastic event, as observed in the quasistatic simulations described in section 0.3. Figures adapted from refs (Picard *et al.*, 2004, Maloney and Lemaitre, 2004b, Tanguy *et al.*, 2006).

elementary strains of opposite signs  $\pm \Delta\epsilon_0$ , so that the macroscopic strain-rate takes the form:

$$\dot{\gamma} = \Delta\epsilon_0 (\mathcal{R}_+ - \mathcal{R}_-) \quad (0.1)$$

with  $\mathcal{R}_\pm$  the rates of forward and backward moves. They are estimated assuming that the work of the external stress corresponding to  $\pm$  hops over activations barriers:

$$\mathcal{R}_\pm = \omega_0 \exp(-E_\pm/kT) \quad (0.2)$$

with  $\omega_0$  a microscopic frequency. Eyring assumes stress induces a linear bias between energy levels, so that the barrier depends linearly on  $\sigma$ :  $E_\pm = E_0 \mp \sigma \Omega_0$ , with  $\Omega_0$  an “activation” volume. This leads to writing the stress/strain-rate relation as:

$$\dot{\gamma} = 2\omega_0 \Delta\epsilon_0 \exp\left(-\frac{E_0}{kT}\right) \sinh\left(\frac{\Omega_0\sigma}{kT}\right) \quad (0.3)$$

Of course, the linearisation of this relationship for small stresses leads to Newtonian behavior, with an Arrhenius viscosity. At large  $\sigma$ , it is customary to keep only the dominant exponential term and write stress as:

$$\sigma = \frac{kT}{\Omega_0} \ln(\tau_0(T)\dot{\gamma})$$

with  $\tau_0(T) = \exp\left(\frac{E_0}{kT}\right) / \omega_0 \Delta\epsilon_0$ .

**Argon’s theory.** Eyring’s formulation relied on a representation of deformation in terms of hops of single atoms or molecules, instead of collective motions. Early representations of plasticity addressed this issue while borrowing from the main frame of Eyring’s works, and in particular the idea that the linear viscous behavior arises from a balance between forward (stress releasing) flips and a “back flux”. In order to take into account the collective character of elementary transitions, Argon (Argon, 1979) argues that the shear zones can be viewed as inclusions which are elastically coupled to the surrounding medium, and postulates that a flip occurs when a zone elastically deforms up to some critical strain, in the range of  $\sim 2 - 4\%$ , at which it becomes unstable. The calculation borrows from Eshelby’s works on martensites (Eshelby, 1957), which offers an analytical framework to estimate the total change in elastic energy due to a change in the internal strain state of an inclusion.

The question is how to take into account the fact that the average stress level biases the elastic potential of a zone. At high temperatures, Argon computes the stress bias at linear order, like Eyring, leading to an expression similar to (0.3). At low temperatures, he performs an imposing treatment of the elastic problem, to arrive at a perturbative, second order, estimate of the effect of stress on the minimum where the system resides. It leads to an expression of the form (Argon, 1979):

$$E_+ \propto \left(1 - \frac{\sigma}{\sigma_c}\right)^2 \quad (0.4)$$

where  $\sigma_c = \mu(T)\epsilon_c$  is a typical scale of the shear stress needed to reach the yield point  $\epsilon_c$ . Using equations (0.1), (0.2) and neglecting the back-flux, equation (0.4) leads to a stress/strain-rate relation of the form:  $\sigma - \sigma_c \propto -(T \ln(\Delta\epsilon_0 \omega_0/\dot{\gamma}))^{1/2}$ . The main interest of this theory is that it captures important features of experimental data on metallic glasses, in particular, (i) an apparent singular behavior in the low- $T$  limit, and (ii) the weak  $\dot{\gamma}$  dependence over a broader range of temperatures (Schuh *et al.*, 2007).

One main limitation of this approach is that it treats perturbatively—at second order—the effect of stress on the elastic potential of a shear transformation zone. This approach must break down if the stress level is sufficiently large to bring a zone near instability, as the system then approaches a catastrophe. There is indeed evidence from numerical simulations that deformation-induced instabilities correspond to a saddle node bifurcation (Malandro and Lacks, 1997, Malandro and Lacks, 1999, Maloney and Lemaitre, 2004a). The energy barrier near instability is thus of the form  $E \propto (1 - \sigma/\sigma_c)^{3/2}$  which, after insertion in equations (0.1) and (0.2) would lead to a stress/strain-rate relation of the form:  $\sigma - \sigma_c \propto -(T \ln(\Delta\epsilon_0 \omega_0/\dot{\gamma}))^{2/3}$ . Already formulated by Caroli and Nozières (Caroli and Nozières, 1996) in the context of dry friction, this argument was brought up recently by Johnson and Samwer (Johnson and Samwer, 2005) for metallic glasses, and successfully compared with experimental data.

**Discussion.** A first objection which should be made against these activation theories is that they treat flips as uncorrelated events. As Bulatov and Argon first noted (Bulatov and Argon, 1994b, Bulatov and Argon, 1994c, Bulatov and Argon, 1994d), however, each rearrangement creates a long-range elastic field (Eshelby (Es-

helby, 1957)), hence alters the stress in the rest of the system. These stress changes can be viewed as mechanical signals which are emitted by flips and may trigger secondary events (Lemaitre and Caroli, 2009). This mechanism shows up strikingly in numerical simulation of athermal systems, via the emergence of avalanche behavior (Maloney and Lemaitre, 2004b, Demkowicz and Argon, 2005, Maloney and Lemaitre, 2006, Bailey *et al.*, 2007, Lerner and Procaccia, 2009, Lemaitre and Caroli, 2009). When these elastic effects are effective, it becomes essential to understand the role of the self-generated stress noise in the activation of plastic events themselves.

A second objection is that the above theories obviously ignore the fact that the energy barriers which limit plastic transformation are broadly distributed (Doliwa and Heuer, 2003a, Doliwa and Heuer, 2003b, Doliwa and Heuer, 2003c). Moreover, as the material is strained, shear transformation zones are driven towards their instability threshold (Maloney and Lemaitre, 2004a, Lemaitre and Caroli, 2007). This is quite different from the situation of a glass undergoing thermal relaxation: here, the distribution of barriers is set by the competition between elastic loading and plastic yielding (Rodney and Schuh, 2009a), and some regions of space could, depending on the parameters, present temporarily, very low energy barriers. Rather than being set a priori, the relevant barriers distribution must thus result from a complex dynamical process.

Third, activation theories of plasticity ignore the role of fluctuations of local quantities such as free-volume, elastic constants, stresses, etc. As we will see in Section 0.3, however, the idea that yielding can be easily associated with a unique critical value of the local stress or energy is strongly challenged by numerical observations (Tsamados *et al.*, 2008). Moreover, the activation process should depend significantly on details of the atomic packing, in particular via the fluctuations of local elastic moduli (Tsamados *et al.*, 2009), local density or pressure levels (Demkowicz and Argon, 2004, Demkowicz and Argon, 2005, Argon and Demkowicz, 2006).

#### 0.2.4 Dynamics of the local stress field

A number of models (Bulatov and Argon, 1994b, Bulatov and Argon, 1994c, Bulatov and Argon, 1994d, Baret *et al.*, 2002, Picard *et al.*, 2002, Picard *et al.*, 2004, Picard *et al.*, 2005) focus on the local stress field and its dynamics, in order to take into account two important features which were identified in the previous discussion: (i) the fact that loading drives the system towards local instability thresholds, hence that barriers result from a dynamical process (ii) the fact, that rearrangements may interact via their Eshelby stress fields.

The first of these models was proposed by Argon and Bulatov (Bulatov and Argon, 1994a, Bulatov and Argon, 1994b, Bulatov and Argon, 1994c, Bulatov and Argon, 1994d) in a study involving various aspects of plasticity but also of glassy relaxation (Bulatov and Argon, 1994c). They showed that even in the absence of deformation, taking into account long-range interactions between shear transformations could lead to net behavior which resembles that of glassy models incorporating e.g. distributions of timescales. Their model involves a collection of weak zones which are distributed on a triangular lattice. Transformation probabilities are determined from activation theory, with stress-dependent free-energy barriers  $\Delta G^*(\sigma) = \Delta F_0 - \Omega \sigma_{\alpha\beta} \Delta \epsilon_{\alpha\beta}$

where  $\Delta\epsilon_{\alpha\beta}$  is the strain increment of a transforming zone during transition. Only pure shear transformations are allowed for convenience, but this does not exclude dilation which is introduced via a dilation parameter meant to account for how activation energy depends on pressure. Finally, each transformation alters the stress levels in the whole system via a Green tensor, corresponding to the solution of the Eshelby problem. The zone flips are thermally activated, but the barriers depend of the stress sustained by the zones, so that the introduction of this mechanism allows for correlations between flips.

The gist of Bulatov and Argon's viewpoint is that initially, after a quench, many of these weak zones should be far from their threshold as a consequence of annealing. As stress increases, energy barriers decrease, and some flips might occur. For small values of external stresses, only a few zones, sufficiently near their instability thresholds at the end of annealing, will respond. Moreover, as most zones are far from instability, the stress released by these rare flip events is insufficient to trigger secondary events. Initial loading is thus accompanied by few, isolated rearrangements. As stress increases, however, an increasing number of zones come close to their instability thresholds. Mechanical noise then starts to be able to push zone farther away, leading in some cases to localisation.

Two more recent models, strongly inspired by the Argon Bulatov model, have been proposed by Baret and coworkers (Baret *et al.*, 2002) and Picard and coworkers (Picard *et al.*, 2002, Picard *et al.*, 2004, Picard *et al.*, 2005). The model of reference (Baret *et al.*, 2002) has the interesting feature of incorporating a distribution of threshold values for the local yield stress, but uses extremal dynamics to describe the evolution of the system at vanishingly small strain rate. The model of Picard, on the other hand, does not include disorder, but has the advantage of a relative simplicity and of easily incorporating finite strain rate effects. The model describes the evolution of a scalar stress  $\sigma_i$  on a lattice site through an equation of the form

$$\partial_t \sigma_i = \mu \dot{\gamma} + \sum_j G_{ij} \dot{\epsilon}_{j,\text{plast}} \quad (0.5)$$

where  $\mu$  is a shear elastic modulus. The first term describes an elastic loading proportional to an average external strain rate. The second term is the supplementary loading that arises from the plastic activity at all other sites in the system, which is assumed to be transferred instantaneously through an elastic propagator  $G_{ij}$ . This plastic activity  $\dot{\epsilon}_{j,\text{plast}}$  is computed in turn by assuming that any site that reaches a stress beyond some local critical yield  $\sigma_Y$  releases its stress with a time constant  $\tau$ . Numerical studies of the model show that, at low strain rates, zones of persistent plastic activities can be observed, with a typical size that tends to diverge as the strain rate vanishes.

### 0.2.5 Dynamics of distributions

Based on the ideas mentioned above, several approaches have been proposed, which describe the state of the system by the distribution of a scalar variable—corresponding to either stress levels (Hebraud and Lequeux, 1998) or energy barriers (Sollich *et al.*, 1997, Sollich, 1998). They are based on some empirical assumptions that are inspired

by the physical picture of interacting flow defects. In most of these approaches, an assumption of homogeneous deformation is made, so that the description of macroscopic strain localisation is not permitted. Moreover, a scalar description of stress and strain is retained, with the implicit assumption that the scalar stress corresponds to a local shear stress. Despite this apparent simplicity, these models are far richer than simple local constitutive equations, as they introduce in the picture some auxiliary quantity describing the internal state of the system, in the spirit of the "rate and state" models of solid friction (Rice and Ruina, 1983)<sup>1</sup>.

**Hébraud-Lequeux fluidity model.** The simplest of these models is probably the one introduced by Hébraud and Lequeux (Hébraud and Lequeux, 1998). In this model, one deals with an ensemble of sites that can each sustain a stress  $\sigma$ . The central quantity is the probability distribution (pdf)  $P(\sigma, t)$  of the local stress, which is assumed to evolve according to the equation

$$\partial_t P(\sigma, t) = -G_0 \dot{\gamma} \partial_\sigma P(\sigma, t) - \frac{1}{\tau} H(|\sigma| - \sigma_c) P(\sigma, t) + \frac{1}{\tau} \delta(\sigma) \int_{|\sigma'| > \sigma_c} P(\sigma', t) d\sigma' + D \partial_{\sigma^2}^2 P(\sigma, t) \quad (0.6)$$

where the "stress diffusion term"  $D$  is given self consistently by

$$D = \frac{\alpha}{\tau} \int_{|\sigma'| > \sigma_c} P(\sigma', t) d\sigma' \quad (0.7)$$

. Equation 0.6 is a simple evolution equation for the pdf: the first term corresponds to elastic loading at constant strain rate, with an elastic modulus  $G_0$ . The second and third terms correspond to a description of plastic events that take place with a rate  $1/\tau$  for sites that exceed the critical yield stress  $\sigma_c$ ; according to the third term, each plastic event corresponds to a complete release of the stress, which is set equal to zero. The last term describes a "diffusion" along the stress scale, that is the result of the average activity (stress redistribution after loading or unloading) of all other sites. This could also be described as a "stress noise", and the intensity of this noise is taken, according to equation 0.7, to be proportional to the total plastic activity present in the third term of equation 0.6. The coupling parameter  $\alpha$  in eq. 0.7 is the control parameter of the model. It could be interpreted as corresponding to the intensity of the elastic coupling between sites. For small values of  $\alpha$  ( $\alpha < \alpha_c$  the system is jammed, with a vanishing activity  $D = 0$  in the absence of strain, and multiple solutions for  $P(\sigma)$ . In this jammed situation, the model exhibits a nonzero yield stress (the limit of  $\langle \sigma \rangle$  when  $\dot{\gamma}$  goes to zero is nonzero) and a complex rheological behavior. Despite its apparent simplicity, this model illustrates how the introduction of couplings between simple elasto-plastic elements, even when treated at the mean field level, can give rise to a complex collective behavior. Such models can serve as a basis for more complex, non-local fluidity models, as discussed below.

**Soft Glassy Rheology.** The first, very successful example of a model using the dynamics of a distribution function is probably the "Soft Glassy Rheology" approach

<sup>1</sup>Simpler rate and state models involving a single "fluidity" internal parameter have also been proposed in ref. (Picard *et al.*, 2002, Coussot *et al.*, 2002).

of Sollich and coworkers (Sollich *et al.*, 1997, Sollich, 1998). A number of reviews of this approach, which has been very successfully applied to many features of the rheology of soft glasses, including complex strain histories, are available (Cates, 2002). We will therefore limit ourselves to a very brief description of the assumptions underlying this model. The system is a collection of independent elastoplastic elements, each of which is trapped in an energy minimum of depth  $E < 0$  (relative to some zero energy level). Each element is also assigned a strain  $\ell$  that varies linearly with time, and the energy barrier changes with strain as  $E \rightarrow E(\ell) = E + k\ell^2/2$ , where  $k$  is a local modulus. The escape from a potential well (corresponding to the local yield of an element) is governed by an Arrhenius-like factor,  $\tau_{\text{yield}} \sim \exp(-E(\ell)/X)$ . The two key ingredients in the model are (i) a distribution of trap depths that implies, in the absence of external strain and for small values of  $X$ , that the system has a very broad distribution of relaxation times, and is effectively in a glassy state, with a "weak ergodicity breaking" described by the trap model of Bouchaud (Bouchaud, 1992); (ii) the "effective temperature parameter"  $X$ , which activates the dynamics of any given element, and is intended to represent the mechanical noise arising from the yield of all other elements in the sample. The introduction of  $X$  is a recognition that, in many systems, thermal motion alone is not enough to trigger local yield events. The system has to cross energy barriers that are very large compared to typical thermal energies. However, the model suffers from the fact that this parameter is not determined self consistently, and therefore should be considered as adjustable. The Hébraud-Lequeux equations described above can be considered as a first, simplified attempt to obtain self consistency within this type of framework.

### 0.2.6 Classical rate-and-state formulations

**Dynamics of STZ densities.** The models we have described so far rely on the notion of zone flips in a weak sense: they assume macroscopic plastic behavior to be the net effect of sudden local rearrangements which can occur anywhere within the material depending primarily on the local or macroscopic stress level; but their focus is on the processes—the flips—but not on their loci—the zones. Underlying all of these theories is of course the notion that some regions of space present specific traits—low density? modulus?—which facilitate flips.

The STZ model proposed by Falk and Langer (Falk and Langer, 1998), departs from these works in its stricter interpretation of the concept of zones. They are seen as sufficiently well-defined objects, preexisting the occurrence of flips, so that it actually makes sense to speak of their density. It thus becomes a dynamical state variable, somewhat like defect densities in models of crystalline plasticity. Hence, a constitutive law for amorphous solids must include equations of motion for the density and internal state of these zones. Although recent works have introduced tensorial formulations (Langer, 2004), the gist of STZ theory is captured by assuming that zones are two-level ( $\pm$ ) systems, which can produce strain changes  $\pm\Delta\epsilon_0$  only when they undergo  $\pm \rightarrow \mp$  internal transitions. This leads to writing an equation à la Eyring (see (0.1)) for strain-rate as:

$$\dot{\gamma} = \Delta\epsilon_0 (\mathcal{R}_+ n_+ - \mathcal{R}_- n_-) \quad (0.8)$$



where  $n_{\pm}$  stand for the number densities of  $\pm$  zones. The dynamical equations for the number densities  $n_{\pm}$  then take up the form:

$$\dot{n}_{\pm} = -\mathcal{R}_{+} n_{+} + \mathcal{R}_{-} n_{-} + \mathcal{X} \quad (0.9)$$

where the last term accounts for creation/destruction mechanisms which are meant to describe how the mean flow affect zone populations—in practice, it is assumed to depend e.g. on the macroscopic energy dissipation rate.

The rate factors, of course, must then be expressed in terms of parameters such as stress, or density. In particular, a linear dependence in terms of stress will commonly be assumed. But without going into any more details, it is possible to see, following (Falk and Langer, 1998), how the STZ model accounts for the existence of an elasto-plastic transition. Indeed, the strain-rate in equation (0.8) vanishes provided  $\mathcal{R}_{+} n_{+} = \mathcal{R}_{-} n_{-}$ . A jammed state can thus be achieved even with non-zero transition probabilities, for a specific value of the ration  $n_{+}/n_{-} = \mathcal{R}_{-}/\mathcal{R}_{+}$ . Under various assumptions for the transition probabilities and for the creation/destruction term  $\mathcal{X}$  in (0.9), these equations can be constructed to present a steady plastic flow, and a transition from jammed to flow at a limit external stress, in a way which is consistent with expectations.

The Falk-Langer mechanism for jamming, however, is ground for strong critiques of the theory. Indeed, within this framework, jamming is identified with  $\dot{\gamma} = 0$ , or  $\mathcal{R}_{+} n_{+} = \mathcal{R}_{-} n_{-}$ . Therefore the STZ mechanism for “jamming” is that  $\pm$  flips compensate each others effects, even while zone flips continue to occur. This is of course in complete contradiction with the expectation that below threshold a material should in fact present nearly zero plastic activity. This can be usefully contrasted with models following from Bulatov and Argon’s work, in which jamming actually is due to a complete depletion of near threshold soft zones. To phrase it in the STZ framework, the total rate of rearrangements,  $\mathcal{R}_{+} n_{+} + \mathcal{R}_{-} n_{-}$ , would be expected to vanish—or achieve quite small values—below yield stress.

Most of the later work on STZ theory (Lemaître, 2002, Pechenik *et al.*, 2001, Falk *et al.*, 2004, Bouchbinder and Langer, 2009) contains additions which are meant to address this issue, but then the original Falk-Langer mechanism for jamming is bypassed (Lemaître and Carlson, 2004), and the dominant mechanism for jamming becomes a vanishing of the rate  $\mathcal{R}_{\pm}$ . For this reason, it will be useful in the coming section to present free-volume theories, which were precisely meant to account for a vanishing of these rates, before coming back to STZ theory.

**Free-volume and effective temperature.** It is nowadays commonplace for any theorist of the glass transition to frown upon the notion of free-volume. Indeed, there is clear evidence that changes in pressure or density do not suffice to explain the various features of the glass transition (Alba-Simionesco *et al.*, 2002), and the original free-volume theory by Cohen and Turnbull (Turnbull and Cohen, 1970) has not been retained as a valid interpretation of the phenomenon. In the context of plasticity, however, the question is less neatly settled. There is experimental evidence of homogeneous flows in which plasticity does not produce significant free-volume (Heggen *et al.*, 2005), but dilatancy effects have been observed during the formation of shear-bands (Chen and Chuang, 1975, Donovan and Stobbs, 1981, Li *et al.*, 2002). This observation does

not mean that dilatancy actually impacts the stress response and contribute to the instability mechanism: it may as well be just a passive marker of the formation of shear bands. However, in the absence of better understanding of the instability mechanism, the formulation of constitutive equations which take into account dilatancy effects remain an important issue.

The introduction of free-volume dynamics in rate-and-state formulation of plasticity was pioneered by Spaepen as early as the 70's (Spaepen, 1977). It borrows from Cohen and Turnbull's free-volume theory (Turnbull and Cohen, 1970), which was proposed to explain departures from Arrhenius behavior by introducing a variable which would "replace" temperature in activation factors. A material is seen as composed into many sub-systems of local free-volume  $v_i$ . These variables are then assumed to be exponentially distributed (with little justification) and relaxation events are assumed to occur in regions of high free-volume  $v_i > v_0$ , with density  $\propto e^{-v_0/v_f}$ . Spaepen then argues, that the strain-rate must then take up the form (Spaepen, 1977, Heggen *et al.*, 2005):

$$\dot{\gamma} \propto \Delta\epsilon_0 \omega_0 e^{-v_0/v_f} \ln \left( \frac{\Delta\epsilon_0 v_0 \sigma}{2kT} \right) \quad (0.10)$$

To couple the plastic response with changes of density, he proposes to write an evolution equation for the concentration  $c_f = e^{-v_0/v_f}$  of high free-volume defects, in the form:

$$\dot{c}_f = -k_r c_f (c_f - c_{\text{eq}}) \quad (0.11)$$

with a constants  $k_r$  and  $c_{\text{eq}}$ , which depend on temperature and stress. This equation renders the idea that the evolution of  $c_f$  is controlled by two antagonistic effects, (i) deformation introduces dilatancy at a rate supposedly proportional to  $\dot{\gamma}$  and (ii) high free-volume defects occasionally collapse via a "bimolecular" process—whence the form  $c_f^2$ , which determine an equilibrium value  $c_{\text{eq}}$  in steady state.

In this argument, the postulate that density fluctuation are exponentially distributed, or precise form of free-volume creation and destruction terms should of course be questioned—but the same remark can be made of the creation/destruction term  $\mathcal{X}$  in STZ theory (equation (0.9)). A particular oddity in Spaepen's argument is the reference to a "bimolecular" process to explain the disappearance of free-volume, as if high-density defects were actual objects, which were also mobile and likely to collapse whenever they meet. Different free-volume equations were proposed later by Lemaître (Lemaître, 2002, Lemaître and Carlson, 2004), with a different interpretation, in particular, of the destruction process. It is based on the simple remark that if  $v_f$  controls activation mechanisms and evolves in time, then its decay rate should be of the form  $e^{-v_1/v_f}$ , with  $v_1$  an activation volume for the decay process which has no reason to be equal to  $v_0$ . The rate of dilatancy is moreover supposed to be proportional to  $\sigma\dot{\gamma}$ . Introducing the notation  $\chi = v_0/v_f$ , it leads to coupled equations of the form (Lemaître, 2002, Lemaître and Carlson, 2004, Lemaître, 2006),

$$\begin{aligned} \dot{\gamma} &= \Delta\epsilon_0 \omega_0 e^{-1/\chi} \ln \left( \frac{\sigma}{\mu} \right) \\ \dot{\chi} &= -A_0 e^{-\kappa/\chi} + \sigma \dot{\gamma} \end{aligned}$$

which can reproduce various forms of the transient and unsteady response of amorphous materials under shear. This type of equations are central to recent developments of STZ theory (Falk *et al.*, 2004, Bouchbinder and Langer, 2009)—although  $\chi$  is then called an “effective temperature”. Efforts have also been made to justify STZ equations the basis of thermodynamics principles (Bouchbinder and Langer, 2009). This allows to produce macroscopic formulations which mimic transient response or the formation of shear bands (Manning *et al.*, 2007), but at the cost of an always increasing complexity which often make it difficult to pinpoint the role of the diverse assumptions which are introduced.

### 0.2.7 Nonlocal rheology approach

All the works discussed in the previous sections take for granted that some kind of microscopic local heterogeneity governs the stress strain relationship in amorphous materials. As we will see below, this aspect has, in essence, been confirmed by particle based simulation, although the precise characterization of the flow events is still the object of numerous studies. The next question is therefore the description of the spatial organisation of these events, both in terms of large scale fluctuations and of permanent strain localisation. The study of large scale fluctuations is a subject of current interest within particle based or lattice models (Yamamoto and Onuki, 1998, Maloney and Lemaitre, 2004b, Tanguy *et al.*, 2006, Maloney and Lemaitre, 2006, Bailey *et al.*, 2007, Lerner and Procaccia, 2009, Lemaitre and Caroli, 2009), and some aspects will be discussed in section 0.3. Here we would like to discuss recent extensions of the mean field theories described above, that attempt a description of flow heterogeneities based on deterministic partial differential equations. The common point to all the recently proposed approaches is to supplement the homogeneous rheological description associated with a description of the spatial variation of one of the parameters, based on a diffusive kernel (Manning *et al.*, 2007, Goyon *et al.*, 2008, Fielding *et al.*, 2009). For example, in (Manning *et al.*, 2007), the effective temperature parameter  $\chi$  is assumed to obey a diffusion equation, with a diffusion constant that is proportional to the local rate of plastic deformation. In (Fielding *et al.*, 2009), the effective temperature parameter  $X$  of the SGR model obeys a relaxation-diffusion equation, with a source term that can be taken to be either proportional to the rate of local plastic activity or to the rate of energy dissipation. Finally, in (Goyon *et al.*, 2008), it is the fluidity—that is the local value of  $\dot{\gamma}/\sigma$ —that appears inside the diffusive term. All these models have been shown to reproduce various forms of localization, either aiming to model the formation of shear bands in metallic glasses (Manning *et al.*, 2007), or near-wall localization in microfluidics flows of colloidal suspensions (Goyon *et al.*, 2008), or even faults (Daub and Carlson, 2008).

This very important issue currently attracts considerable interest, but it seems from the diversity of these works, and their various claims to actually account for localization, that many forms of diffusive kernels would capture some of the underlying physics, irrespectively of their actual microscopic assumptions. We must hence worry about the severity of tests provided by fitting such lengthscales. Clearly, it seems important to assess how sensitive the resulting behavior is on particular forms of the

diffusive terms, in other words, to break the frontiers between different groups where these various equations are developed, and put them in parallel for close comparison.

At the microscopic level, the specific mechanisms which justify diffusive terms, will still have to be specified, as there are currently only very few attempts to do so. At present, the only theoretical attempt to justify the use of a diffusive kernel on the basis of a more microscopic approach can be found in ref. (Bocquet *et al.*, 2009). This reference introduces a systematic coarse graining approach of the lattice elasto-plastic model of ref. (Picard *et al.*, 2004), which eventually results in a coupling between a local rheology described by the Hébraud-Lequeux model with equation (0.7) being replaced by a nonlocal relation between stress diffusivity and the rate of plastic activity. In other words, the stress diffusivity—in stress-space—is caused by the plastic activity in the vicinity of the zone under concern—in real space. The Laplacian form of this contribution can be easily understood, as a purely linear gradient in plastic activity leads to a local compensation between neighboring zones with higher and lower activities.

These approaches are particularly attractive and will be amenable to a direct comparison with numerical data obtained from elasto-plastic lattice models or from particle based simulations, and probably with experiments. Such comparisons will be, in a first stage, based on the predictions for strain localisation and the characteristic length/times over which this phenomenon is predicted to take place. Further refinements, e.g. including tensorial aspects for the stress tensor, will be necessary to actually predict mechanical response under various sollicitations.

### 0.2.8 Conclusion

**What effective temperature?** It is clear from the preceding discussion that rate-and-state formulations of plasticity should be seen as various forms of empiricism, rather than actual microscopic theories. This does not, however, discount the fact that they do reproduce many features of experimental data. This is particularly striking in view of the simplicity of most of these formulations which do not involve complex, distribution-like state variables—like Hébraud-Lequeux or SGR. And of course, rate-and-state equations are potentially quite important are they can easily be incorporate in Navier-Stokes equations, and used to study flows with complex geometries.

It is striking that, taken as an empirical attempt to replace temperature in activation factors by another arbitrary quantity, the introduction of free-volume parallels—and anticipate (Spaepen, 1977)—the recourse to the notion of “effective temperature” (Cugliandolo *et al.*, 1997, Berthier *et al.*, 2000, Barrat and Berthier, 2001, Berthier and Barrat, 2002, Ono *et al.*, 2002, Haxton and Liu, 2007) which seems more acceptable in today’s language. These practices emphasize the necessity to understand low-temperature activation mechanisms. Clarifying whether they involve stress noise, local fluctuation of pressure, density—like the free-volume theories would argue—or even moduli, however, remain a largely opened issue.

Free-volume models have the merit to make a specific, testable (Spaepen, 1977, Heggen *et al.*, 2005), assumption about the relation of activation factors with density. Sollich argues (Sollich *et al.*, 1997, Sollich, 1998), that the effective temperature should represent the noise produced by ongoing rearrangements. Yet, as long as the link

between “noise temperature” and defect densities is not established, it seems that these two different families of theories introduce the concept to take into account quite different forms of disorder. In fact, both mechanical noise and local fluctuations in moduli are present (Yoshimoto *et al.*, 2004), and both are related to the underlying distribution of local barrier height which, as we have discussed previously is determined by a dynamic interplay between elastic loading and plastic activity itself. In this regard, it is significant that the STZ and free-volume models require to introduce dynamical equations for their effective temperature.

**What zones?.** The notion of a shear transformation is inevitably rather fuzzy as, in practice, rearrangements are hard to identify and isolate in space or time. However, it offers a useful framework to rationalize observations, and articulate theories. Phenomenologies of plasticity based on this premise, must still specify a number of assumptions about flips, mainly in order to answer two questions: what triggers a flip? how much does a flip contribute to stress relaxation and energy dissipation?

These questions, at the core of the construction of theories, have motivated a number of numerical and experimental studies, and some results will be discussed in section 0.3. The aim is to attempt to check the basic assumptions contained in the theoretical description, and to identify the parameters which should be incorporated into theories. This is of course difficult because zones are not easily identified within the disordered structure, and because material properties, such as elastic moduli strongly fluctuate. Basically, it can be said that a consensus is now established on the fact that elementary flips can be identified at low temperature, and produce a stress release characterized by a quadrupolar symmetry in two dimensions. Many questions, regarding in particular the conditions that trigger a flip, or the distribution of stress drops, remain to be explored accurately. The situation in three dimensions is even more complex, and even the form of the stress field released after one flip has not been studied in any detail. The interaction between flips, the way a local rearrangement changes the probability for a subsequent flip to take place nearby, and the associated time scales, are also subjects of current interest which should be clarified and used as inputs of a theoretical description.

## 0.3 Particle based simulations

### 0.3.1 Introduction

Particle based simulations, and in particular molecular dynamics (MD) simulations of systems under shear have a long history, as they have been used very early to determine the viscosity of simple fluids. A number of tools have been developed in this context, that allow one to integrate the equations of motion for an ensemble of a several thousands of interacting particles submitted to conditions of constant (or possibly oscillatory) strain rate, or sometimes to conditions of constant stress. Possible local heating associated with the shear are taken care of using thermostats that do not perturb the shear flow (except possibly at very high shear rates which will not be discussed in this paper). Another “trick” that allows one to mimic shear in large systems is the use of Lees-Edwards boundary conditions, in which the usual square (cubic) box periodicity is replaced by that of a tilted Bravais lattice, with a

tilt angle corresponding to a deformation that increases linearly with time. As a result the system undergoes a shear deformation driven by the boundaries of the simulation cell. In some cases these Lees-Edwards boundary conditions will be supplemented by a procedure that supplements the boundary driven deformation with the imposition of an homogeneous local deformation. In quasistatic deformations (see below), this is achieved by rescaling the particle coordinates at each strain step  $\delta\epsilon$ , in an affine manner e.g.  $X' = X + Y \times \delta\epsilon$ . In MD simulations an algorithm called the SLLOD algorithm (Allen and Tildesley, 1989) is used to modify in a similar way the evolution of the velocity along  $x$ ,  $dv_x/dt = F_x/m + \dot{\epsilon}v_y$ , so that a linear velocity profile is immediately obtained after application of shear.

In the context of glassy systems, the shear rate is of course an essential quantity, that provides a natural time scales in systems in which the relaxation time is essentially infinite. Particle based simulations are rather limited in terms of the time scales, with simulation times that are at best of the order of  $10^6$  microscopic vibrational periods. While this may seem very high (the corresponding shear rate, for a metallic system, would be of the order of  $10^8 s^{-1}$ ) an important feature is that a reasonable scale separation between the microscopic, vibrational time scale and the time scale of the deformation is achieved. A common assumption, confirmed to some extent by results described below, is that this time scale separation is sufficient to make such simulations representative of the qualitative behavior in deformed glassy systems, in spite of the unphysically high rates used.

An alternative to these finite shear rate calculations is to use zero temperature, quasistatic simulations. In these simulations the system is always in a local energy minimum. After each elementary deformation step, which is described by an affine transformation of the particle coordinates, the energy is minimized again to the "nearest" minimum using a conjugate gradient or steepest descent algorithm. Note that this "nearest minimum" may, strictly speaking, depend on the minimisation algorithm. Here the notion of time step and duration of the simulation is totally absent, and is replaced by that of elementary strain step and of total deformation at the end of the simulation. The elementary deformation step is limited by the need to avoid an artificial "tunneling" through energy barriers during the elementary deformation. While this cannot be, strictly speaking, avoided, experience shows that elementary step strains of the order of  $10^{-5}$  are small enough to limit such problems and to produce reproducible trajectories. As each step strain requires a careful minimization, achieving large deformations with the quasistatic method is computationally costly. However, the method has the advantage of providing a well defined, "zero shear rate, zero temperature" limit for the flow behavior of the system.

A critical issue in the study of glassy systems using simulations is that of equilibration. The properties of a glass are known to depend strongly on the preparation route and on the quenching rate, which is un-physically high in simulations. The mechanical properties under for small deformations are expected to be affected by the preparation history; however, if a large and homogeneous deformation can be achieved, the memory of the initial configuration will be erased, and the results will not depend on the preparation route. Note that the hypothesis of a deformation that remains homogeneous at large scales is important here, and that different preparation routes may

lead to samples that display a stronger tendency to strain localization, without ever undergoing the homogeneous deformation that would erase its memory. Such effects were described in a model glass with partial quasicrystalline order in ref. (Shi and Falk, 2006).

Many different systems have been explored under shear using either quasistatic or finite shear rate simulations, periodic (Lees Edwards) cells or driving by external walls. The studies published in the literature vary considerably in their choices for interaction potentials and also in the type of quantities that are characterized in the flowing systems. Broadly speaking, one may distinguish three types of interaction potentials: mixtures of particles interacting by Lennard-Jones type potentials, that are generally used with the intention of modeling either metallic glasses (Srolovitz *et al.*, 1981), or colloidal suspensions (Stevens and Robbins, 1993). Interactions with strong directional bonding, that are suitable for systems such as amorphous silicon or silica (Argon and Demkowicz, 2006), and contact interactions, that are used to model granular systems (Combe and Roux, 2000) or foams (Durian, 1995)(Langer and Liu, 1997). Polymers have also been extensively simulated (Argon *et al.*, 1995), in general using Lennard-Jones type interactions with extra intramolecular bonding that gives rise to strain hardening at large strain under traction.

Particle based simulations offer the possibility to obtain, within the time and length scales permitted by simulation, all microscopic information that can be obtained from particle coordinates. As often, the main difficulty is to find the appropriate tools to analyze the extensive information that is available to extract the information relevant to the flow process and its heterogeneity. In the following, we describe some of the generic aspects that emerge from these studies, without attempting an exhaustive literature review. We will distinguish results obtained at relatively high  $T$ , where the thermal fluctuations are important compared to those associated with the deformation, and low temperature results at which microscopic motion originates essentially from the external driving.

### 0.3.2 Finite temperature MD

At finite temperatures, the local motion of particles is a complex superposition of thermal and of deformation induced movements. The identification of specific plastic events associated with the deformation is not possible. In practice, this situation is encountered if the temperature is close to the glass transition temperature  $T_g$ , so that the systems at rest usually display significant ageing. The tools appropriate to analyze this regime are largely inherited from studies of the liquid glass transition. A number of studies have focused on the global (macroscopic) stress strain relation, and the occurrence of macroscopic, shear banding instabilities. In spite of the short time scales explored by simulations, stress strain curves exhibit a behavior that is remarkably similar to the one observed in experiments. The peak stress in the curves shown in figure 0.1 depends on shear rate and on the "age" of the system, i.e. on the preparation history (Varnik *et al.*, 2004). This dependence was rationalized by Röttler and Robbins (Röttler and Robbins, 2005) on the basis of "rate and state" ideas borrowed from solid friction. The peak stress varies as a logarithmic function of the strain rate and of the age of the system

$$\sigma_{max} = \sigma_0 + s_0 \ln \theta + s_1 \ln \dot{\gamma} \quad (0.12)$$

where  $\theta$  is an effective age of the system, that depends on the waiting time after the quench and before the train, and on the time spent under strain. This type of behavior is somewhat similar to what could be expected in a simple Eyring description, with the yield stress being associated with activated events of well defined energy., that could be a function of the waiting time (Rottler and Robbins, 2005) , However the coefficients do not behave as expected in such a description, and in particular the coefficient  $s_1$  tends to be constant rather than proportional to temperature, which implies that some a different description of activation has to be found.

MD simulations have developed in several directions. Attempts to get a better understanding of activation mechanisms (Ilg and Barrat, 2007, Haxton and Liu, 2007), studies of strain localisation at intermediate scales, and studies of correlation functions that would allow the detection of microscopic dynamical heterogeneities. (Onuki and Yamamoto, 1998, Yamamoto and Kim, 2000). Studies of activation tend to support the notion of an effective temperature that would determine the rate at which the system overcomes local energy barrier, and that depends on both temperature and shear rate. Haxton and Liu (Haxton and Liu, 2007) claim that a data collapse for the flow curve can be achieved on this basis, with a single parameter  $T_{eff}(T, \dot{\gamma})$ . They further argue, that this effective temperature is itself given by the fluctuation dissipation ratio in the system, determined for various observables (Berthier and Barrat, 2002), (O'Hern *et al.*, 2002).. A slightly different approach was chosen in ref (Ilg and Barrat, 2007), in which an artificial "reaction coordinate" of a bistable system was coupled to a system under shear, and an Arrhenius behavior with a shear rate dependent effective temperature was reported. While this points to the existence of a mechanical noise that would complement -or even replace - the thermal noise, no progress has been made that would allow one to relate the intensity of the noise to the shear rate. A clear justification of the SGR "effective temperature" approach from microscopic simulations is therefore still missing.

Persistent strain localisation in the form of "shear bands" has been observed in a relatively small number of MD simulation studies, in 2 as well as 3 dimensions. In general such a localisation is observed under strain conditions that are not fully periodic, but rather induced by boundaries (either in pure shear or uniaxial conditions). In (Varnik *et al.*, 2003), this localisation was observed at the walls of the simulation cell in isothermal simulations. Other examples of strain localisation are obtained under uniaxial loading with free boundaries (Shi and Falk, 2005a, Shi and Falk, 2006) , multi-axial loading (Bailey *et al.*, 2004), or nanoindentation (Shi and Falk, 2005b) sometimes using a notch as initiator. These studies have not resulted in a clear understanding of the microscopic of shear bands, as mentioned in (Bailey *et al.*, 2004), "there is much that is not understood about shear bands. This not only includes why they form in the first place, but also what determines their width, what distinguishes them structurally from the surrounding material...". Simulation studies seem to indicate that some kind of initial heterogeneity (e.g. boundaries) is important in the formation mechanism. Structural differences concerning the local bond order environment or local potential energy inside the shear band have been reported in some systems (Shi and Falk, 2005a, Li and Li, 2006), but they are not observed in all simulations (Varnik *et al.*,



2003). In the system studied by Shi and Falk (Shi and Falk, 2005*a*), the quench procedure was also shown to modify the ability to form shear bands. In rapidly quenched samples higher strain rates lead to increased localization, while the more gradually quenched samples exhibit the opposite strain rate dependence.

Finally, we mention that indications of large scale dynamical heterogeneities have been found in early simulation work by Yamamoto and Onuki (Yamamoto and Onuki, 1998) on sheared systems of soft spheres. These authors studied the spatial correlations between bond breakage events defined over a small, fixed time windows. Indications of critical behavior in the quasistatic limit are found in this work, which can be seen as a precursor of more detailed studies of 4 point correlations. Such correlations are studied in some more detail in (Furukawa *et al.*, 2009) which shows for example anisotropy of dynamical heterogeneity in the non newtonian regime. There is certainly, however, much room for a detailed study of dynamical heterogeneities in sheared systems at finite temperature as a function of temperature and strain rate.

### 0.3.3 The zero-temperature solid

Molecular dynamics methods can thus mimic various features of material response which are commonly seen in experiments. But they are of course limited by the timescales they can access, which are orders of magnitude smaller than physical ones in numerical models of metallic glasses—the situation is not as dramatic if we seek to model e.g. colloidal glasses. They permit to access detailed information about the structure and dynamics. But the microscopic motions are very blurred by thermal fluctuations, and it turns out to be quite difficult in practice to extract relevant information.

At finite but low temperature—lower than  $T_g$ —a glass would typically spend most of the time vibrating around a single local minimum in the potential energy landscape. One thus expects that this vibrational component bring a trivial contribution while the most interesting aspects of dissipation in material response are controlled by hops between local minima—which may in some cases be thermally-activated. Therefore, after many works on glassy relaxation (Stillinger, 1995, Debenedetti and Stillinger, 2001, Doliwa and Heuer, 2003*a*, Doliwa and Heuer, 2003*b*, Doliwa and Heuer, 2003*c*), it makes sense to try to separate vibrations from hopping in PEL.

If temperature is taken to zero and in the absence of an external drive, the system would just reach one local minimum and rest there. When studying the response of a material to strain, this zero temperature limit permits to focus on deformation-induced changes of local minima (Malandro and Lacks, 1997, Malandro and Lacks, 1999). We will see that it already captures many important aspects of the elasto-plastic response.

**Deformation-induced changes in PEL.** Let us thus consider a numerical model of a glass at rest in a local minimum. This configuration could have been produced by annealing followed by an energy minimization protocol, or it could be the results of minimization starting from the configuration obtained after some plastic deformation has been sustained by the system.

We first consider the case when this minimum is stable and the applied deformation small enough to preserve stability. We introduce a strain parameter  $\gamma$ . At zero temperature, the positions of the particles in the local minimum—that is as they adapt

to the imposed deformation to preserve mechanical equilibrium—are smooth functions  $\{\vec{r}_i(\gamma)\}$  of strain. This comes with an important consequence, as these strain-induced changes are reversible. In other words the material response is *exactly, microcanonically*, reversible. The system behaves as a perfectly elastic material.

Studies of elasticity in this regime date back to the works of Born and Huang (Huang, 1950, Born and Huang, 1954), who proposed to compute elastic constants by assuming that the relative displacements of all particles are affine, i.e. match the macroscopic strain. With this assumption, it is immediately possible to predict elastic moduli from the pair correlation function. The problem is that the particle trajectories  $\{\vec{r}_i(\gamma)\}$ , which trace strain-induced changes of a local minimum, are not simply dictated by macroscopic deformation. This approximation is only valid for very simple crystals, but not for glasses, and the displacement  $\{\vec{r}_i(\gamma)\}$  contains, in general, some non-affine contribution.

The existence of a non-affine component to the displacement field has been known for a long time, and its existence was hinted at in various papers as a trace of disorder (Alexander, 1998). But it was really brought to the front scene as it appeared (Leonforte *et al.*, 2005) that they affected significantly the values of the macroscopic elastic moduli. The existence of a non affine field reflects the disorder in local elastic moduli, which results in an heterogeneous elastic response exhibiting long ranged correlations (DiDonna and Lubensky, 2005, Maloney, 2006). This heterogeneity has been characterized in detail using a systematic coarse-graining approach (Tsamados *et al.*, 2009), with the results that below a scale of a few tens of particle sizes the elastic constants (and especially the shear moduli) differ significantly from their macroscopic values.

Analytical expressions are available (Maloney and Lemaître, 2004a, Lemaître and Maloney, 2006) for the non-affine field and for the corrected moduli. They correspond to the zero-temperature limit of those proposed by Lutsko at finite temperature (Lutsko, 1988). The important point is that the  $T = 0$  non-affine field takes up the form:

$$\frac{d\vec{r}_i}{d\gamma} = -\mathcal{H}_{ij}^{-1} \cdot \vec{\Xi}_j \quad (0.13)$$

where  $\mathcal{H}$  is the Hessian matrix, and  $\vec{\Xi}$  a vector field corresponding to infinitesimal, strain-induced, changes of forces on each particles. As  $\vec{\Xi}$  can be constructed from the derivatives of the potential function, it is easy to show that it does not vanish or present any singular behavior. Consequently the non-affine displacements will catch any singular contribution coming from the inversion of a Hessian matrix. Since glasses present many low-lying modes, the non-affine field will pick up information about the existence of soft regions in space (Papakonstantopoulos *et al.*, 2008, Tsamados *et al.*, 2009), these soft regions precisely which control plasticity, when a material is driven by strain towards instabilities (Lemaître and Caroli, 2007).

Although it is, in principle, outside the scope of this review, we briefly mention the special case of granular systems interacting through repulsive contact forces. At zero temperature, these systems loose their rigidity abruptly as the density is decreased, which defines the (un)jamming transition. In the vicinity of the jamming density, the non affine, heterogeneous response becomes the dominant feature in the elastic

deformation of such systems (van Hecke, 2010), and can be associated with a diverging "isostatic" length scale, below which the stability is governed by boundary conditions (Wyart, 2005).

**Plastic events in AQS shear.** The AQS (athermal quasi-static) protocol consists in applying quasi-static deformation to the zero-temperature solid described previously. It is implemented by a two-steps protocol (Malandro and Lacks, 1997, Malandro and Lacks, 1999, Maloney and Lemaitre, 2004*b*, Maloney and Lemaitre, 2006). Starting from an equilibrium configuration: (i) the system is deformed homogeneously by a very small increment; (ii) energy is minimized. If the increments are sufficiently small, the system will be able to track continuously deformation-induced changes of the occupied minimum. As the procedure is iterated, the local minimum will eventually become unstable. Minimization will then let the system relax to a new configuration which is disconnected from the previous one. On a flow curve, as illustrated on Fig. 0.1, the AQS response shows up as a series of continuous branches—corresponding to the reversible tracking of single minima—and discontinuous jumps—corresponding to "plastic events".

The elastic response being perfectly reversible, the plastic events account exactly for all of dissipation, and the serrations of the stress curve permit to identify them unambiguously. This has made possible detailed studies their organization in space and of their size distribution (Maloney and Lemaitre, 2004*b*, Maloney and Lemaitre, 2004*a*, Tanguy *et al.*, 2006, Maloney and Lemaitre, 2006, Bailey *et al.*, 2007, Lerner and Procaccia, 2009).

In some cases, single shear transformations can be observed. This can be done by looking at events of small sizes, which are present in the steady state flow (Maloney and Lemaitre, 2004*b*, Maloney and Lemaitre, 2006), but more easily found during the early loading phase from an annealed, isotropic state (Tanguy *et al.*, 2006). Another way to access them is to look at the onset of plastic events, which were found to involve a single eigenvalue going to zero (Malandro and Lacks, 1997, Malandro and Lacks, 1999, Doye and Wales, 2002). Close to instability, the non-affine field (see Eq. 0.13) aligns with the vanishing mode and the singular behavior of energy, stresses and moduli can even be predicted (Maloney and Lemaitre, 2004*a*). This has permitted to study the spatial structure of this mode (Maloney and Lemaitre, 2006, Tanguy *et al.*, 2006), showing that it generically presents the quadrupolar structure and the decay away from its center, which are predicted by the Eshelby inclusion model (Eshelby, 1957, Picard *et al.*, 2004).

But in steady flow—that is passed some preparation-dependent initial transient (Tanguy *et al.*, 2006)—plastic events are not in general composed of single zone flips but typically involve many of them collectively organized as avalanches (Maloney and Lemaitre, 2004*b*, Maloney and Lemaitre, 2004*a*, Maloney and Lemaitre, 2006, Bailey *et al.*, 2007, Lerner and Procaccia, 2009). This last claim is supported, in particular, by measurements of the average size of stress (resp. energy) drops, which scale as  $L^\beta$  (resp.  $L^\alpha$ ) with system size  $L$ , and  $\alpha, \beta < 1$ . Despite some differences in the reported exponents, this power law scaling is now accepted as a fact, and proves that the local rearrangements are strongly correlated, in notable contradiction with the mean-field assumption.

**Avalanches at finite strain rates.** An immediate question is whether avalanches are only a feature of the quasi-static limit, or whether they exist for realistic values of the external parameters. In particular, the unfolding of each avalanches should indeed take some time, determined by the duration of elementary flips and by the times of propagations of elastic signal between flip events (Lemaitre and Caroli, 2009). Even if we stick with athermal systems, as soon as a finite strain rate is introduced, the avalanches may start to overlap because of their finite duration. Hence they can no longer be properly identified as in the quasi-static limit.

So, a first problem when going away from the AQS limit is to define valid observables which allow one to characterize the existence of an underlying avalanche process, i.e. of correlations between local rearrangement events. A protocol has thus been designed to characterize avalanches in 2D athermal systems, from measurements of transverse diffusion (Lemaitre and Caroli, 2009). The principle starts from the observations that in AQS simulations, the transverse diffusion constant presents strong size dependence (Lemaitre and Caroli, 2007, Maloney and Robbins, 2008). This dependence can then be attributed to the organization of Eshelby flips along roughly linear patterns (Lemaitre and Caroli, 2009), so that the diffusion constant can be expressed as a function of a typical avalanche size.

This observations has led to propose that the avalanche size should depend on the strain-rate as  $\ell \propto 1/\dot{\gamma}^{1/d}$  in dimension  $d$  (Lemaitre and Caroli, 2009). As  $\dot{\gamma}$  decreases, the avalanche size should saturate at a length-scale  $\propto L$  below some critical strain-rate  $\gamma_c \propto 1/L^d$ , an in any usual cross-over. This suggestion is based on an interpretation of the avalanche size as being limited by the screening of Eshelby elastic signals by the background noise due resulting from all the flips in the system.

These scalings are consistent with the rough scaling of the average stress drop as  $\langle \sigma \rangle \propto 1/L$  found in (Maloney and Lemaitre, 2004b, Maloney and Lemaitre, 2006), but of course, these estimates remain rough, and it not ruled out that more precise measurements would provide slightly different exponents consistent with the values of  $\beta$  found in (Lerner and Procaccia, 2009). What should remain, however, is that avalanches are present at all physically accessible strain rates, even when they overlap in time, even when they cannot be accessible via the identification of separated events.

**Steps towards a phenomenology of plasticity.** The observation of avalanches, and their properties in the quasi-static limit and at finite strain rates provides clear benchmarks for future theories of plasticity. Yet, as usual in studies of amorphous systems, we can observe and characterize the avalanche process; we can conclude that some form of correlation exist between flip events; but the underlying mechanisms which promote these correlations remain quite difficult to identify. In fact, several processes must concur to make the avalanching behavior possible.

First, the flip-flip interaction must be mediated in some way. Here, the medium is elastic and this is know to produce long-ranged effects. The Eshelby mechanism (Eshelby, 1957, Argon, 1979, Bulatov and Argon, 1994b, Bulatov and Argon, 1994c, Bulatov and Argon, 1994d) must play a central role, namely, each flip alters the stress in its surroundings, which may push a nearby region passed its instability threshold, hence trigger a secondary instability. The existence of this mechanism is supported by the observation of single flips in AQS simulations (Maloney and Lemaitre, 2004a, Tanguy

*et al.*, 2006), by the measurement of the stress decay in space (Maloney and Lemaitre, 2006), and by direct visualisation of flips events at finite strain rates (Lemaitre and Caroli, 2009). There are also now direct observations that a primary zone flip can push a nearby one closer to instability (Lemaitre and Caroli, 2007, Lemaitre and Caroli, 2009), thus showing that the Eshelby mechanism is fully at work.

But we must note also that when a system is sheared from an carefully annealed, isotropic, state zone flips tend to be isolated instead of organizing as avalanches (Tanguy *et al.*, 2006). There is no reason why there should be any fundamental difference between the basic mechanisms which are at work during the loading phase or in steady state. Therefore, the difference between the early stage response and the steady-state flow must indicate that the state of material evolves under loading (Lerner and Procaccia, 2009), in a way which increases the density of near-threshold, soft, zones, in consistence with the idea that strain progressively results in advection of the zones towards their instability thresholds (Lemaitre and Caroli, 2007). In steady state, the density of near-threshold regions is high, and the domino effect due to the Eshelby stress redistribution operates efficiently. In early loading, the density of near-threshold regions would be lower if the system is carefully annealed, thus permitting to identify more easily isolated events.

Like in a game of dominoes, the Eshelby mechanism makes the avalanching process possible. But it can intervene only if the density of near-threshold regions is high enough, which must be a property of the material structure. The question thus comes back up again to be able to characterize the regions or “zones” where elementary shear transformation may occur. Could we identify them a priori? What would be their density? Do they correlate with some property of the local structure—stress, density, moduli? Up to now, the particle based studies that have addressed these questions have resulted rather disappointing results. First of all, it appears that the regions in which the localized plastic events take place are not, in general, under particularly high stress. More precisely, the probability of observing a yield event in a region under high stress is also higher, but this is balanced by the fact that the number of such regions is small. A good correlation, on the other hand, has been established between yield events and regions with low values of elastic moduli (Tsamados *et al.*, 2009). This suggests that the heterogeneity of local elastic constants should be taken into account in more coarse-grained models. Unfortunately, the local elasticity is already a rather complex property, and attempts to directly relate the probability of yielding to the local atomic structure have not been very successful, although a correlation with the shape of the Voronoi volume was observed in polymer glasses (Papakonstantopoulos *et al.*, 2008). In systems with strongly directional bonding such as amorphous silicon, a correlation could also be established between the density of bonding defects and the local plastic activity (Talati *et al.*, 2009). One must acknowledge that a link is still missing that would allow a better control of plastic properties directly from the design of the microscopic structure.

## 0.4 Perspectives

We close this review by emphasizing a few key issues which, in our opinion, have to be addressed in order to build a consistent theory of amorphous solids under strain,

including the heterogeneous, fluctuating aspects. Most of these points have been discussed in detail in the previous sections.

The present consensus on the existence and importance of "zones" and "flips" as the essential building blocks of the plastic activity makes it strongly desirable to have a better understanding of these zones from the standpoint of the local microstructure. Many more atomistic simulations, involving efficient sampling techniques allowing for longer simulation runs (Rodney and Schuh, 2009*b*), and using various types of interatomic potentials, will be needed to achieve such an understanding. It might even be the case that a predictive search for microstructural characteristics of flipping zones is illusory, and that the local plastic activity is a result from so many factors that it is essentially unpredictable.

Even if the flips are not associated with well defined zones at the structural level, the essential features of the current models of elasto-plastic behavior are in fact statistical in nature. It is therefore essential to develop tools that allow one to quantify in an unbiased, statistical manner the plastic activity, so that a comparison between models, numerical simulations and experiments is possible. Such a strategy has proven very successful in the field of glassy systems and supercooled liquids at rest, and should be extended to the case of low temperature, driven amorphous systems. In particular, a statistical description of dynamical heterogeneities in strained systems, a quantification of avalanche distributions (in energy and size), and of the relevant correlation lengths, is still missing. The influence of temperature and strain rate on this quantities should also be a subject of interest.

Finally, we made in the introduction a distinction between the heterogeneities associated with statistical fluctuations of a globally homogeneous strain, and the "macroscopic", long lived heterogeneities described as strain localization. The description of the latter situation has made some progress recently, with the realization that a mechanism involving the diffusion of some auxiliary state variable (fluidity, effective temperature, free volume) was in general needed to produce such heterogeneities. This auxiliary variable could even be related to some of the statistical aspects mentioned above. However, all these approaches are still oversimplified (scalar stress variable, absence of convection...) so that direct comparison with a realistic experimental setups is difficult.

## **Acknowledgements**

We acknowledge many useful discussions and collaborations with Lydéric Bocquet, Christiane Caroli, Peter Sollich, Anne Tanguy, Michel Tsamados.

# References

- Alba-Simionesco, C, Kivelson, D, and Tarjus, G (2002). *J. Chem. Phys.*, **116**(12), 5033.
- Alexander, S (1998). *Physics Reports*, **296**, 65.
- Allen, M.A. and Tildesley, D.J. (1989). *Computer Simulation of Liquids*.
- Argon, A. S. (1979). *Acta Met.*, **27**, 47.
- Argon, A. S. (1982). *J. Phys. Chem. Solids*, **43**, 945.
- Argon, A. S., Bulatov, V. V., Mott, P. H., and Suter, U. W. (1995). *J. Rheol.*, **39**, 377.
- Argon, A. S. and Demkowicz, M. J. (2006). *Philosophical Magazine*, 4153.
- Argon, A. S. and Kuo, H. Y. (1979). *Mater. Sci. Eng.*, **39**, 101.
- Bailey, N.P., Schiotz, J., and Jacobsen, K.W. (2004). *Phys. Rev. B*, **69**, 144205.
- Bailey, N. P., Schiotz, J., Lemaitre, A., and Jacobsen, K. W. (2007). *Phys. Rev. Lett.*, **98**, 095501.
- Baret, J. C., Vandembroucq, D., and Roux, S. (2002). *Phys. Rev. Lett.*, **89**, 195506.
- Barrat, JL and Berthier, L (2001). *Phys. Rev. E*, **63**, 012503.
- Berthier, L, Barrat, JL, and Kurchan, J (2000). *Phys. Rev. E*, **61**, 5464.
- Berthier, L. and Barrat, J.-L. (2002). *Phys. Rev. Lett.*, **89**, 95702.
- Bocquet, L., Colin, A., and Ajdari, A. (2009). *Phys. Rev. Letters*, **103**, 036001.
- Born, M. and Huang, K. (1954). *Dynamical Theory of Crystal Lattices*. Clarendon Press, Oxford.
- Bouchaud, J.-P. (1992). *Journal de Physique I*, **2**, 1705.
- Bouchbinder, E. and Langer, J. S. (2009). *Phys. Rev. E*, **80**, 031132.
- Brader, J. M., Cates, M. E., and Fuchs, M. (2008). *Phys. Rev. Letters*, **101**, 138301.
- Bulatov, V. V. and Argon, A. S. (1994a). *J. Non-Cryst. Solids*, **172**, 876.
- Bulatov, V. V. and Argon, A. S. (1994b). *Model. Simul. Mater. Sci. Eng.*, **2**, 167.
- Bulatov, V. V. and Argon, A. S. (1994c). *Model. Simul. Mater. Sci. Eng.*, **2**, 185.
- Bulatov, V. V. and Argon, A. S. (1994d). *Model. Simul. Mater. Sci. Eng.*, **2**, 203.
- Caroli, C. and Nozières, P. (1996). In *Physics of sliding friction* (ed. B. Persson and E. Tosatti), Volume 311, Series E: Applied Sciences, Dordrecht. NATO ASI Series: Kluwer Acad. Publ.
- Cates, M.E. (2002). In *Nonequilibrium dynamics and slow relaxations in condensed matter* (ed. J.-L. Barrat, M. Feigelman, J. Kurchan, and J. Dalibard), Proceedings of the 57th Les Houches Summer school. Springer, Berlin.
- Chen, HS and Chuang, SY (1975). *Appl. Phys. Lett.*, **27**, 317.
- Combe, G. and Roux, J.-N. (2000). *Phys. Rev. Lett.*, **85**, 3628.
- Coussot, P. (2005). *Rheometry of Pastes, Suspensions, and Granular Materials: Applications in Industry and Environment*. Wiley.
- Coussot, P., Nguyen, Q.D. and Huynh, H.T., and Bonn, D. (2002). *Phys. Rev.*



- Lett.*, **88**, 175501.
- Cugliandolo, LF, Kurchan, J, and Peliti, L (1997). *Phys. Rev. E*, **55**, 3898.
- Daub, E.G. and Carlson, J.M. (2008). *Journal of Geophysical Research-Solid Earth*, **113**, B12309.
- Debenedetti, P.G. and Stillinger, F.H. (2001). *Nature*, **400**, 259.
- Demkowicz, M. J. and Argon, A. S. (2004). *Phys. Rev. Letters*, **93**, 025505.
- Demkowicz, M. J. and Argon, A. S. (2005). *Phys. Rev. B*, **72**, 245206.
- DiDonna, BA and Lubensky, TC (2005). *Phys. Rev. E*, **72**, 066619.
- Doliwa, B. and Heuer, A. (2003a). *Phys. Rev. E*, **67**, 031506.
- Doliwa, B. and Heuer, A. (2003b). *Phys. Rev. E*, **67**, 030501(R).
- Doliwa, B. and Heuer, A. (2003c). *Phys. Rev. Lett.*, **91**, 235501.
- Donovan, PE and Stobbs, WM (1981). *Acta. Met.*, **29**, 1419.
- Doye, J. P. K. and Wales, D. J. (2002). *J. Chem. Phys.*, **116**, 3777.
- Durian, D. J. (1995). *Phys. Rev. Lett.*, **75**, 4780.
- Eshelby, J. D. (1957). *Proc. Roy. Soc. London A*, **241**, 376.
- Falk, M. L., Langer, J.S., and Pechenik, L. (2004). *Phys. Rev. E*, **70**, 011507.
- Falk, M. L. and Langer, J. S. (1998). *Phys. Rev. E*, **57**, 7192.
- Fielding, S. M., Cates, M. E., and Sollich, P. (2009). *Soft Matter*, **5**, 2378.
- Fuchs, M. and Cates, M. E. (2002). *Phys. Rev. Lett.*, **89**, 098301.
- Furukawa, A., Kim, K., Saito, S., and Tanaka, H. (2009). *Phys. Rev. Letters*, **102**, 016001.
- Furukawa, A. and Tanaka, H. (2006). *Nature*, **443**, 434.
- Goyon, J., Colin, A., Ovarlez, G., Ajdari, A., and Bocquet, L. (2008). *Nature*, **454**, 84.
- Haxton, T. K. and Liu, A. J. (2007). *Phys. Rev. Letters*, **99**, 195701.
- Hebraud, P and Lequeux, F (1998). *Phys. Rev. Lett.*, **81**, 2934.
- Heggen, M, Spaepen, F, and Feuerbacher, M (2005). *J. Appl. Phys.*, **97**, 033506.
- Helfand, E and Fredrickson, GH (1989). *Phys. Rev. Lett.*, **62**, 2468.
- Huang, Kun (1950). *Proc. Roy. Soc. London A*, **203**, 178.
- Ilg, P. and Barrat, J. L. (2007). *Europhys. Letters*, **79**, 26001.
- Johnson, WL and Samwer, K (2005). *Phys. Rev. Letters*, **95**, 195501.
- Langer, J.S. (2004). *Phys. Rev. E*, **70**, 041502.
- Langer, S. A. and Liu, A. J. (1997). *J. Phys. Chem. B*, **101**, 866.
- Larson, RG (1999). *The Structure and Rheology of Complex Fluids*. Oxford University Press, Oxford.
- Lemaître, A. (2002). *Phys. Rev. Lett.*, **89**, 195503.
- Lemaitre, A (2006). In *Jamming, Yielding, and Irreversible Deformation in Condensed Matter* (ed. Miguel, MC and Rubi, JM), Volume 688, Lecture Notes in Physics, p. 129.
- Lemaître, A and Carlson, J (2004). *Phys. Rev. E*, **69**, 061611.
- Lemaitre, A. and Caroli, C. (2007). *Phys. Rev. E*, **76**, 036104.
- Lemaitre, A. and Caroli, C. (2009). *Phys. Rev. Letters*, **103**, 065501.
- Lemaître, A. and Maloney, C.E. (2006). *J. Stat. Phys.*, **123**, 415.
- Leonforte, F., Boissière, R., Tanguy, A., Wittmer, J. P., and Barrat, J.-L. (2005). *Phys. Rev. B*, **72**, 224206.

- Lerner, E. and Procaccia, I. (2009). *Phys. Rev. E*, **79**, 066109.
- Li, J, Spaepen, F, and Hufnagel, TC (2002). *Phil. Mag. A*, **82**, 2623.
- Li, QK and Li, M (2006). *Appl. Phys. Lett.*, **88**, 241903.
- Lubliner, J (2008). *Plasticity Theory*. Dover Publications.
- Lutsko, J. F. (1988). *J. Appl. Phys.*, **64**, 1152–1154.
- Malandro, Dennis L. and Lacks, Daniel J. (1997). *J. Chem. Phys.*, **107**, 5804.
- Malandro, D. L. and Lacks, D. J. (1999). *J. Chem. Phys.*, **110**, 4593.
- Maloney, C. and Lemaitre, A. (2004a). *Phys. Rev. Lett.*, **93**, 16001.
- Maloney, C. and Lemaitre, A. (2004b). *Phys. Rev. Lett.*, **93**, 195501.
- Maloney, C. E. (2006). *Phys. Rev. Lett.*, **97**, 035503.
- Maloney, Craig E. and Lemaitre, A (2006). *Phys. Rev. E*, **74**, 016118.
- Maloney, C. E. and Robbins, M. O. (2008). *J. Phys. Cond. Matt.*, **20**, 244128.
- Manning, M. L., Langer, J. S., and Carlson, J. M. (2007). *Phys. Rev. E*, **76**, 056106.
- Miguel, MC and Zapperi, S (2006). *Science*, **312**, 1151.
- O’Hern, C. S., Langer, S. A., Liu, A. J., and Nagel, S. R. (2002). *Phys. Rev. Lett.*, **88**, 075507.
- Ono, IK, O’Hern, CS, Durian, DJ, Langer, SA, Liu, AJ, and Nagel, SR (2002). *Phys. Rev. Lett.*, **89**, 095703.
- Onuki, A. and Yamamoto, R. (1998). *J. Non-Cryst. Solids*, **235**, 34.
- Papakonstantopoulos, G.J., Riggleman, R.A., Barrat, J-L, and de Pablo, J. J. (2008). *Phys. Rev. E*, **77**, 041502.
- Pechenik, L., Rabinowitz, D. J., and Langer, J. S. (2001). , **46**, 1023.
- Picard, G., Ajdari, A., Bocquet, L., and Lequeux, F. (2002). *Phys. Rev. E*, **66**, 051501.
- Picard, G., Ajdari, A., Lequeux, F., and Bocquet, L. (2004). *European Phys. Journal E*, **15**, 371.
- Picard, G., Ajdari, A., Lequeux, F., and Bocquet, L. (2005). *Phy. Rev. E*, **71**, 010501(R).
- Rice, J.R. and Ruina, A.L. (1983). , **105**, 343.
- Rodney, D. and Schuh, C. (2009a). *Phys. Rev. Lett.*, **102**, 235503.
- Rodney, David and Schuh, Christopher A. (2009b). *Phys. Rev. B*, **80**, 184203.
- Rottler, J. and Robbins, M. O. (2005). *Phys. Rev. Lett.*, **95**, 225504.
- Rouxel, T., Ji, H., Hammouda, T., and Moreac, A. (2008). *Phys. Rev. Lett.*, **100**, 225501.
- Schall, P., Weitz, D. A., and Spaepen, F (2007). *Science*, **318**, 1895.
- Schuh, Christopher A., Hufnagel, Todd C., and Ramamurty, Upadrasta (2007). *Acta Mat.*, **55**, 4067.
- Shi, Y. F. and Falk, M. L. (2005a). *Phys. Rev. Letters*, **95**.
- Shi, Y. F. and Falk, M. L. (2005b). *Applied Physics Letters*, **86**, 011914.
- Shi, Y. F. and Falk, M. L. (2006). *Phys. Rev. B*, **73**.
- Sollich, P (1998). *Phys. Rev. E*, **58**, 738.
- Sollich, P, Lequeux, F, Hebraud, P, and Cates, ME (1997). *Phys. Rev. Letters*, **78**, 2020.
- Spaepen, F. (1977). *Acta Met.*, **25**, 407.
- Srolovitz, D., Maeda, K., and Egami, T. (1981). *Phil. Mag. A*, **44**, 847.

- Stevens, Mark J. and Robbins, Mark O. (1993). *Phys. Rev. E*, **48**, 3778.
- Stillinger, F. H. (1995). *Science*, **267**, 1935.
- Talati, M., Albaret, T., and Tanguy, A. (2009). *Europhysics Letters*, **86**, 66005.
- Tanguy, A., Leonforte, F., and Barrat, J. L. (2006). *European Physical Journal E*, **20**, 355.
- Tsamados, M., Tanguy, A., Goldenberg, C., and Barrat, J.-L. (2009). *Phys. Rev. E*, **80**, 026112.
- Tsamados, M., Tanguy, A., Leonforte, F., and Barrat, J. L. (2008). *European Physical Journal E*, 283.
- Turnbull, D and Cohen, MH (1970). *J. Chem. Phys.*, **52**, 3038.
- Utz, M., Debenedetti, P. G., and Stillinger, F. H. (2000). *Phys. Rev. Lett.*, **84**, 1471.
- van Hecke, M. (2010). *J. Phys. Cond. Matt.*, **22**, 033101.
- Varnik, F., Bocquet, L., and Barrat, J. L. (2004). *J. Chem. Phys.*, **120**, 2788.
- Varnik, F., Bocquet, L., Barrat, J. L., and Berthier, L. (2003). *Phys. Rev. Letters*, **90**, 095702.
- Wyart, M (2005). *Annales de physique*, **30**, 1.
- Yamamoto, R. and Kim, K. (2000). *J. Phys. IV*, **10**, 15.
- Yamamoto, R and Onuki, A (1998). *Phys. Rev. Letters*, **81**, 4915.
- Yoshimoto, K, Jain, TS, Workum, KV, Nealey, PF, and de Pablo, JJ (2004). *Phys. Rev. Letters*, **93**, 175501.