



HAL
open science

MOF Formation vs. Reversible High Ligand Uptake in Anhydrous Halides: Two Opposing Aspects of $3\infty[\text{La}_2\text{Cl}_6(4,4'\text{-bipy})_5]\bullet 4(4,4'\text{-bipy})$

Christoph J. Höller, Philipp Matthes, Jens Beckmann, Klaus Mueller-Buschbaum

► To cite this version:

Christoph J. Höller, Philipp Matthes, Jens Beckmann, Klaus Mueller-Buschbaum. MOF Formation vs. Reversible High Ligand Uptake in Anhydrous Halides: Two Opposing Aspects of $3\infty[\text{La}_2\text{Cl}_6(4,4'\text{-bipy})_5]\bullet 4(4,4'\text{-bipy})$. *Journal of Inorganic and General Chemistry / Zeitschrift für anorganische und allgemeine Chemie*, 2009, 636 (2), pp.395. 10.1002/zaac.200900359 . hal-00542553

HAL Id: hal-00542553

<https://hal.science/hal-00542553>

Submitted on 3 Dec 2010

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



**MOF Formation vs. Reversible High Ligand Uptake in
 Anhydrous Halides: Two Opposing Aspects of $^3\infty[\text{La}_2\text{Cl}_6(4,4'\text{-bipy})_5]\bullet 4(4,4'\text{-bipy})$**

Journal:	<i>Zeitschrift für Anorganische und Allgemeine Chemie</i>
Manuscript ID:	zaac.200900359.R1
Wiley - Manuscript type:	Article
Date Submitted by the Author:	28-Sep-2009
Complete List of Authors:	Höller, Christoph J.; Ludwig-Maximilians Universitaet Muenchen, Department Chemie und Biochemie Matthes, Philipp; Ludwig-Maximilians Universitaet Muenchen, Department Chemie und Biochemie Beckmann, Jens; Freie Universität Berlin, Institut für Chemie und Biochemie Mueller-Buschbaum, Klaus; Ludwig-Maximilians Universitaet Muenchen, Department Chemie und Biochemie
Keywords:	Metal Organic Frameworks, Lanthanum, Ln-N-MOFs, Reversibility, 4,4'-bipyridine



1
2
3 **MOF Formation vs. Reversible High Ligand Uptake in Anhydrous Halides:**
4
5 **Two Opposing Aspects of ${}^3\infty[\text{La}_2\text{Cl}_6(4,4'\text{-bipy})_5]\cdot 4(4,4'\text{-bipy})$**
6
7

8
9 **Christoph J. Höller^a, Philipp Matthes^a, Jens Beckmann^b and Klaus Müller-**
10 **Buschbaum^{a*}**
11

12
13
14 ^a München, Department für Chemie und Biochemie, Ludwig-Maximilians-Universität

15
16 ^b Berlin, Institut für Chemie und Biochemie - Anorganische Chemie, Freie Universität
17

18
19
20 Received...

21
22
23 *Dedicated to Professor Hans-Jörg Deiseroth on the Occasion of his 65th Birthday.*
24
25

26
27 **Abstract.** Construction of the framework structure ${}^3\infty[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ (**1**), bipy = 4,4'-
28
29 bipyridine, $\text{C}_{10}\text{H}_8\text{N}_2$, is achieved by reaction of the anhydrous halide LaCl_3 with molten 4,4'-
30
31 bipyridine. Five equivalents of bipyridine are used for the framework construction linking
32
33 LaCl_3 units to give an extended, three-dimensional MOF. Furthermore four additional equiva-
34
35 lents of bipyridine per LaCl_3 unit are incorporated within the crystalline MOF, which is
36
37 thereby completely filled with bipy molecules. This compound formation results in the ex-
38
39 traordinary high uptake of nine equivalents of bipyridine per equivalent of the formula LaCl_3
40
41 and a volume increase of eight times the volume of LaCl_3 . Further heating of the MOFs re-
42
43 sults in a stepwise release of all nine equivalents of bipyridine and re-formation of the anhy-
44
45 drous chloride at 425 °C. Formation and disassembly can be run in cycles and are reversible.
46
47 Thus two interesting yet opposing aspects are the reversible construction and disassembly of
48
49 the MOF framework.
50
51
52
53
54

55
56
57 **Keywords:** Metal Organic Frameworks; Lanthanum; Ln-N-MOFs; Reversibility, 4,4'-
58
59 bipyridine
60

* Priv.-Doz. Dr. Klaus Müller-Buschbaum
Department für Chemie und Biochemie
Ludwig-Maximilians-Universität München
Butenandt Str. 5-13 (D)
D-81377 München
Fax: 0049 (0)89 2180 77851
E-Mail: kmbch@cup.uni-muenchen.de

Introduction

Usually the construction of MOFs is described as an intended one way reaction of metal salts and complexes with a suitable linker to give a multi-dimensional framework structure [1 – 6]. The way back and thereby decomposition of the MOF structures is fairly unwanted. This includes the N-ligand containing Ln-N-MOFs we have elaborated from ligand melts [7]. Nonetheless decomposition is a prominent feature of all solvent containing MOFs that enforce a thermal activation in order to gain porous materials by evaporation of incorporated solvate ligands [8 – 10]. As collapse of the referring frameworks is likely for highly solvent containing MOFs it is also limiting the interest in such materials. We discovered for the series of two-dimensional 4,4'-bipyridine containing Ln-N-MOFs of the formula $\frac{2}{\infty}[\text{Ln}_2\text{Cl}_6(\text{bipy})_3]\cdot 2\text{bipy}$, with Ln = Ce, Pr, Nd, Sm, Eu, Tb, bipy = 4,4'-bipyridine, $\text{C}_{10}\text{H}_8\text{N}_2$, [11] that their formation is thermally reversible. Construction of the MOFs and disassembly into the reagents can be directed depending on the temperature. We now found that the number of equivalents that are reversibly incorporated in LnX_3 can be further increased for lanthanum up to nine equivalents per formula unit including the reversible character of the reactions. Accordingly, formation and disassembly reactions of MOFs can be equally interesting for such a high and reversible ligand uptake in anhydrous halides of the rare earth elements.

Experimental

All manipulations were carried out under inert atmospheric conditions using glove box, ampoule as well as vacuum line techniques. Heating furnaces were equipped with Al₂O₃ tubes and EUROTHERM 2416 control elements. For ${}^3_{\infty}[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ (**1**) the trichloride LaCl₃, was prepared according to the known ammonium halide route [12] using the oxide La₂O₃ (ChemPur, 99.9%), HCl solution (10 mol/l, reagent grade) and ammonium chloride (Fluka, 99.5%), and purified by decomposition of the trivalent ammonium chlorides under vacuum and subsequent sublimation of the products. 4,4'-bipyridine (ACROS, 98%) was used as purchased. All products are air and moisture sensitive. The IR spectra were recorded using a BRUKER FTIR-IS66V-S spectrometer. KBr pellets for Mid IR investigation and PE pellets for Far IR were used under vacuum. Only of the crystalline product was used for micro analyses on a Vario Microcube (Elementar) elemental analyzer. The yield of the reaction was calculated according to the amount of ligand used for the synthesis. For thermal analysis the bulk product of ${}^3_{\infty}[\text{La}_2\text{Cl}_6(4,4'\text{-Bipy})_5]\cdot 4(4,4'\text{-Bipy})$ was studied using simultaneous DTA/TG (TG-DTA92 Setaram). 17,5 mg of ${}^3_{\infty}[\text{La}_2\text{Cl}_6(4,4'\text{-Bipy})_5]\cdot 4(4,4'\text{-Bipy})$ were heated from 25 °C to 700 °C in a constant He-flow of 50ml/min with a heating rate of 10°C/min.

Synthesis of ${}^3_{\infty}[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$:

LaCl₃ (0.25 mmol, 62 mg) and 4,4'-bipyridine (bipy, 1.25 mmol, 195 mg) were sealed in an evacuated DURANTM glass ampoule and heated to 90° C in 7 h and then to 120° C within 30h. The temperature was held for 48 h and then cooled to 95° C in 250 h and finally to room temperature in another 14 h. The reaction resulted in high reflecting colourless crystals of the product and an amount of unreacted LaCl₃ in the bulk. Yield: 199 mg = 84 %. Anal. calc. La₂Cl₆C₉₀H₇₂N₁₈; M = 1896.22 g mol⁻¹: C, 57.01; N, 13.30; H, 3.83. Found: C, 56.74; N, 12.98; H, 3.95. MIR (KBr): (3129 s, 1591 m, 1532 w, 1489 w, 1403 s, 1231 w, 1066 w, 1011

1
2
3 w, 868 w, 822 msh, 801 s, 733 w, 614 m, 571 w, 474 w) cm^{-1} . FIR (PE): (570 m, 474 m, 236
4
5 w, 214 m, 179 m, 160 w, 143 w) cm^{-1} .
6
7

8 **Studies concerning the reversibility of formation and disassembly of the framework com-**
9 **ound were performed with the same amounts of the reagents but shortened in annealing and**
10 **reaction times for each step. Only one tenth, 24 h annealing and one half, 24 reaction time**
11 **were applied. Therefore no complete reaction occurred and the crystallinity degrades. These**
12 **conditions were chosen in order to keep a reasonable timeframe for multiple repetitions.**
13 **Therefore an amount of 25 % of unreacted halide LaCl_3 remains.**
14
15
16
17
18
19
20
21
22
23
24


25 *Crystal Structure Determination*

26
27 The best suitable single crystal of the compound ${}^3_{\infty}[\text{La}_2\text{Cl}_6(4,4'\text{-Bipy})_5]\cdot 4(4,4'\text{-Bipy})$ (**1**) was
28 selected for single crystal X-ray investigation under glovebox conditions and sealed in a glass
29 capillary. Data collection was carried out on a STOE IPDS-II diffractometer (Mo K_{α} radiation
30 $\lambda = 0.7107 \text{ \AA}$) at 170 K. The structure was determined using direct methods [13]. All non-H
31 atoms were refined anisotropically by least squares techniques [14]. All hydrogen positions
32 were calculated into pre-set positions adjusting their thermal parameters to 1.2 of the referring
33 carbon atoms. The compound crystallizes in the triclinic space group $P-1$. Due to the free ro-
34 tation of the pyridine rings in 4,4'-bipyridine one incorporated bipy molecule is disordered
35 (see Supplementary Material). Integrity of symmetry and extinction were checked and no
36 higher symmetry could be found [15]. A numerical absorption correction was applied [16].
37
38 For crystallographic data see Table 1. Further information was deposited at the Cambridge
39 Crystallographic Data Centre, CCDC, 12 Union Road, Cambridge CB2 1EZ, UK (fax: +44
40 1223336033 or e-mail: deposit@ccdc.cam.ac.uk) and may be requested by citing the deposi-
41 tion number CCDC-740032, the names of the authors and the literature citation.
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60


Results and Discussion

Reversible Formation and High Ligand Uptake

We elaborated that the use of melts of organic ligands like N-heterocyclic amines is a suitable alternative to solvent treatments if co-coordination of the solvent is to be avoided [17]. Depending on the ligands used and the reaction conditions a large structural variety ranging from small molecular complexes [17a, 18] to coordination polymers and MOFs [19] can be obtained. The ligand melt can be directly used for oxidizing reactive metals like the lanthanides acting as weak N-H acids using various activation methods for the metals [17a, 20]. The method can also be used for other ligands like phenols [21] or thioles [22] to yield amides, phenolates and thiolates of the rare earth elements together with hydrogen gas. It can be further expanded to ligands that cannot be utilized in a redox reaction. Instead of metals, we successfully used anhydrous halides of the rare earth elements to yield nitriles [23] of the lanthanides including the first dinitrile Ln-N-MOFs of the referring elements [24, 25]. Accordingly, the 4,4'-bipyridine ligand that has been used for MOF constructions of transition metals already [26 – 28] was most promising for our synthesis strategy together with lanthanide halides. 4,4'-bipyridine acts as chemical scissors and cuts down the halide structure. It also controls the formation of coordination polymers by interlinking LnCl₃ units. For numerous lanthanides this can lead to 2D-nets of the formula $\frac{2}{\infty}[\text{Ln}_2\text{Cl}_6(\text{bipy})_3] \cdot 2\text{bipy}$, with Ln = Ce, Pr, Nd, Sm, Eu, Tb, [11]. In addition to three interlinking ligands per two LnCl₃ units two equivalents of bipy are incorporated in cavities within and in-between the sheets. For the larger trivalent ion La³⁺ we now found that an extraordinary increase in the 4,4'-bipyridine uptake is observed according to the reaction:



At temperatures starting from 155 °C the MOF begins to release the incorporated bipyridine equivalents in three steps. Removal of the template bipyridine is in principle possible by evaporation, as thermal investigations reveal. But as this does not lead to suitable crystals, it has yet not been possible to refine the structure of this new template free high temperature compound. At temperatures between 330 – 425 °C also the linking bipyridine equivalents are released in two steps under re-formation of LaCl₃, as observed by simultaneous DTA/TG (see Figure 1):



If the bipy equivalents released from the MOF are recovered, the formation reaction can be started over. Thus formation and disassembly of the framework are reversible. Formation and disassembly can be run in cycles as powder diffraction indicates, (see Figure 2) [29]. Some unreacted LaCl₃ in the product pattern originates from incomplete reaction due to shorter reaction and annealing times, that had to be chosen in order to allow multiple reversible processes in a reasonable timeframe. Reversibility is further supported by IR spectroscopy. Mid IR spectra of the product contain bands that can be identified with the ν(C-N) stretching modes. They are shifted to smaller wave numbers compared to the free ligand because of binding to the metal ions and thus weakening of the C-N bonds at 1011 cm⁻¹. The ν(C=N) ring vibrations of the uncoordinated 4,4'-bipyridine are observed at 1591 cm⁻¹. Furthermore, the Far IR spectra of framework **1** contain bands that indicate ν(Ln-N) stretching modes between 236 – 214 cm⁻¹ [30]. Only the Ln-Cl stretching and deformation bands at 571 and 474 cm⁻¹ [31] are found after disassembly.

That leads us to describing the compound presented here with two equally interesting features: As the first feature a MOF structure is formed that is able to incorporate a large number of additional bipy equivalents as well as these incorporated molecules can all be

1
2
3 thermally released. Moreover, as the linking bipyridine equivalents can also be released re-
4 versibly, another interesting point can be raised as the second feature: Anhydrous halides
5 LnX₃ can show an extraordinary high uptake of the organic ligand 4,4'-bipyridine under for-
6 mation of N-donor complexes as thermal intermediates and re-formation of the halides at suit-
7 able temperatures.
8
9
10
11
12
13
14
15
16

17 *Crystal Structure*

18
19 The crystal structure of ${}^3_{\infty}[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ (**1**), bipy = 4,4'-bipyridine, C₁₀H₈N₂, consti-
20 tutes to a three-dimensional framework. It is built up by trivalent lanthanum ions linked by
21 4,4'-bipyridine ligands and chloride ions. ${}^3_{\infty}[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ exhibit a C.N. of eight con-
22 sisting of three halide atoms each as well as two additional N atoms, resulting in a double N
23 capped trigonal prism around La. Three bipyridine ligands coordinate rather symmetrically μ -
24 $\eta^1:\eta^1$ to two different lanthanide cations with each N atom of the pyridine rings. The double
25 capping N atoms exhibit an N–La–N angle of 135.7(2)° (ideal 120°). A fourth bipyridine
26 molecule coordinates end-on η^1 to only one lanthanide ion. Four chloride ions complete the
27 coordination sphere of every La atom (see Figure 3, for selected interatomic distances and
28 angles see Table 2). Edge sharing of the double capped trigonal prisms leads to the formation
29 of a three-dimensional framework. The C.N. of La in **1** is higher than for the series of lantha-
30 nides of the formula ${}^2_{\infty}[\text{Ln}_2\text{Cl}_6(\text{bipy})_3]\cdot 2\text{bipy}$, with Ln = Ce, Pr, Nd, Sm, Eu, Tb [11], which
31 exhibit pentagonal-bipyramidal coordination. This corroborates the fact that La³⁺ is the largest
32 of the Ln³⁺ ions [32]. Double capped trigonal prisms around La atoms can also be found in
33 La₃OCl[AsO₃]₂ as well as in [La₂(aib)₄(H₂O)₈](ClO₄)₆ (aib = α - aminoisobutyric acid) [33,
34 34], although the most numerous coordination polyhedron for La³⁺ with C. N. eight is the
35 square antiprism, especially regarding N coordination [35]. The La–N distances in **1** range
36 from 274.9(4) – 281.8(4) pm. Due to the large La³⁺-ion and the high coordination number of
37 eight, the La–N distances are about 20 pm larger than the ones e.g. found for
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

$^2_\infty[\text{Sm}_2\text{Cl}_6(\text{bipy})_3]\cdot 2\text{bipy}$ of 258 – 263 pm [11]. In $^3_\infty[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ two of the chloride ions also link between different lanthanide ions forming a “double bridge” [36]. The La–Cl distances range from 276.0(2) – 296.4(2) pm and match with the trichloride [37]. Figure 4 depicts the crystal structure of **1**.

As the linkage leads to a complicated crystal structure, it is reasonable to reduce it to a topological description. $^3_\infty[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ can be identified with two perpendicular 2D-nets that each have a 6,3 topology. Viz., three six-fold bridged rings form a 2D-layer. This gives an overall 3D-(6,4) topology (see Figure 5). This topology is e.g. also found for MOFs like $\text{Co}(\text{Im})_2$ ($\text{Im}^- = \text{N}_2\text{C}_3\text{H}_3$, imidazolate) or $[\text{Eu}(\text{pdc})_{1,5}(\text{dmf})]\cdot \text{dmf}\cdot (\text{H}_2\text{O})_{0.5}$ ($\text{pdc}^{2-} =$ pyridine-3,5-dicarboxylate, $\text{dmf} =$ dimethylformamid) [38, 39]. The topology description however is based on counting the chloride “double-bridges” as one bridge only. Otherwise the connectivity would be five.

Acknowledgment. We thank the *Deutsche Forschungsgemeinschaft* for supporting this work by the project “3D-Raumnetze komplexer Selten-Erd-Amide, ein Weg zu neuartigen MOFs“, *Prof. Dr. W. Schnick* and the *LMU München* for the excellent conditions, and the *Wilhelm-Klemm-* and the *Dr. Otto-Röhm-Gedächtnis-Foundation* for their support.

References

- [1] O. M. Yaghi, H. Li, C. Davis, T. Richardson, *Acc. Chem. Res.* **1998**, *31*, 474.
- [2] T. Loiseau, C. Serre, C. Hugeunard, G. Fink, G. Taulelle, M. Henry, T. Bataille, G. Férey, *Chem. Eur. J.* **2004**, *10*, 1373.

- 1
2
3 [3] P. Horcajada, C. Serre, M. Vallet-Reg, M. Sebban, F. Taulelle, G. Ferey, *Angew.*
4
5 *Chem.* **2006**, *118*, 6120; *Angew. Chem. Int. Ed.* **2006**, *45*, 5974.
6
7
8 [4] W. Lin, W. J. Rieter, K. M. L. Taylor, *Angew. Chem.* **2009**, *121*, 660; *Angew. Chem.*
9
10 *Int. Ed.* **2009**, *47*, 2.
11
12 [5] S. S. Han, H. Furukawa, O. M. Yaghi, W. A. Goddard III, *J. Am. Chem. Soc.* **2008**,
13
14 *130*, 11580.
15
16
17 [6] S. Bauer, N. Stock, *Chem. Unserer Zeit* **2008**, *42*, 12.
18
19
20 [7] a) K. Müller-Buschbaum, S. Gomez-Torres, P. Larsen, C. Wickleder, *Chem. Mater.*
21
22 **2007**, *19*, 65; b) K. Müller-Buschbaum, Y. Mokaddem, F. Schappacher, R. Pöttgen,
23
24 *Angew. Chem.* **2007**, *119*, 4463; *Angew. Chem. Int. Ed.* **2007**, *46*, 4385; c) J.-C.
25
26 Rybak, K. Müller-Buschbaum, *Z. Anorg. Allg. Chem.* **2009**, *635*, 1134; d) K. Müller-
27
28 Buschbaum, Y. Mokaddem, *J. Chem. Soc., Chem. Commun.* **2006**, 2060.
29
30
31 [8] H. Hayashi, A. P. Cote, H. Furukawa, M. O'Keeffe, O. M. Yaghi, *Nature Mat.* **2007**,
32
33 *6*, 501.
34
35
36 [9] Q.-R. Fang, G.-S. Zhu, Z. Jin, Y.-Y. Ji, J.-W. Ye, M. Xue, H. Yang, Y. Wang, S.-L.
37
38 Qiu, *Angew. Chem.* **2007**, *119*, 6758; *Angew. Chem. Int. Ed.* **2007**, *46*, 6638.
39
40
41 [10] G. Ferey, C. Serre, C. Mellot-Draznieks, F. Millange, S. Surble, J. Dutour, I. Margi-
42
43 olaki, *Angew. Chem.* **2004**, *116*, 6456; *Angew. Chem. Int. Ed.* **2004**, *43*, 6296.
44
45
46 [11] C. J. Höller, M. Mai, C. Feldmann, K. Müller-Buschbaum, *J. Chem. Soc., Dalton*
47
48 *Trans.*, submitted.
49
50
51 [12] G. Meyer, *Inorg. Synth.* **1989**, *25*, 146.
52
53 [13] G. M. Sheldrick, *SHELXS-97, Program for the resolution of Crystal Structures*,
54
55 Göttingen **1986**.
56
57 [14] G. M. Sheldrick, *SHELXL-97, Program for the refinement of Crystal Structures*,
58
59 Göttingen **1997**.
60

- 1
2
3 [15] A. L. Spek, PLATON-2000, *A Multipurpose Crystallographic Tool*; V1.07, University
4 of Utrecht **2003**.
5
6
7
8 [16] STOE Software Package, *V.1.16, X-RED, Program for the numerical absorption*
9 *correction*, Darmstadt **2001**.
10
11
12 [17] a) K. Müller-Buschbaum, *Z. Anorg. Allg. Chem.* **2005**, *631*, 811; b) K. Müller-
13 Buschbaum, C. C. Quitmann, *Eur. J. Inorg. Chem.* **2004**, 4330; c) K. Müller-
14 Buschbaum, Y. Mokaddem, *Eur. J. Inorg. Chem.* **2006**, 2000; d) C. C. Quitmann, K.
15 Müller-Buschbaum, *Z. Anorg. Allg. Chem.* **2005**, *631*, 1191.
16
17
18 [18] a) K. Müller-Buschbaum, C.C. Quitmann, *Inorg. Chem.* **2003**, *42*, 2742; b) G. B. Dea-
19 con, C. M. Forsyth, A. Gitlits, B. W. Skelton, A. H. White, *J. Chem. Soc. Dalton*
20 *Trans.* **2004**, 1239; c) C. C. Quitmann, V. Bezugly, F. R. Wagner, K. Müller-
21 Buschbaum, *Z. Anorg. Allg. Chem.* **2006**, *632*, 1173.
22
23 [19] a) K. Müller-Buschbaum, *Z. Naturforsch.* **2006**, *61b*, 792; b) K. Müller-Buschbaum,
24 Y. Mokaddem, *Solid State Sci.* **2008**, 416; c) K. Müller-Buschbaum, Y. Mokaddem, *Z.*
25 *Anorg. Allg. Chem.* **2008**, *634*, 2360.
26
27 [20] a) K. Müller-Buschbaum, C. C. Quitmann, *Inorg. Chem.* **2006**, *45*, 2678; b) C. C.
28 Quitmann, K. Müller-Buschbaum, *Angew. Chem.* **2004**, *116*, 6120; *Angew. Chem. Int.*
29 *Ed.* **2004**, *43*, 5994; c) K. Müller-Buschbaum, *Z. Anorg. Allg. Chem.* **2004**, *630*, 895.;
30 d) G. Meyer, *Z. Anorg. Allg. Chem.* **2008**, *634*, 201; e) K. Müller-Buschbaum, Y.
31 Mokaddem, C. J. Höller, *Z. Anorg. Allg. Chem.* **2008**, *634*, 2973.
32
33 [21] G. Deacon, P. C. Junk, S. G. Stuart, *Z. Anorg. Allg. Chem.* **2004**, *630*, 1541.
34
35 [22] A. Zurawski, E. Wirnhier, K. Müller-Buschbaum, *Eur. J. Inorg. Chem.* **2009**, 2482.
36
37 [23] a) C. C. Quitmann, K. Müller-Buschbaum, *Z. Anorg. Allg. Chem.* **2004**, *630*, 573.; b)
38 C. J. Höller, K. Müller-Buschbaum, *Z. Anorg. Allg. Chem.* **2007**, *633*, 2614.
39
40 [24] C. J. Höller, K. Müller-Buschbaum, *Inorg. Chem.* **2008**, *47*, 10141.
41
42 [25] C. J. Höller, M. Döblinger, K. Müller-Buschbaum, *Eur. J. Inorg. Chem.*, submitted.
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

- 1
2
3 [26] B. Moulton, E. B. Rather, M. J. Zaworotko, *Crystal Engineering* **2001**, *4*, 309.
4
5
6 [27] M. Felloni, A. J. Blake, N. R. Champness, P. Hubberstey, C. Wilson, M. Schröder, *J.*
7
8 *of Supermol. Chem.* **2002**, *2*, 163.
9
10 [28] K. O. Kongshaug, H. Fjellvag, *J. Solid State Chem.* **2003**, *175*, 182.
11
12 [29] STOE WINXPOW v.1.04, *Program package for the operation of powder diffracto*
13 *meters and analysis of powder diffractograms*, Darmstadt **1999**.
14
15 [30] J. Weidlein, U. Müller, K. Dehnicke, *Schwingungsfrequenzen II. G. Thieme Verlag,*
16 *Stuttgart* **1986**.
17
18 [31] K. Nakamoto, *Infrared and raman spectra of inorganic and coordination compounds,*
19 *New York* **1978**.
20
21 [32] R. D. Shannon, *Acta Crystallogr.* **1976**, *A32*, 751.
22
23 [33] D.-H. Kang, T. Schleid, *Z. Anorg. Allg. Chem.* **2007**, *633*, 1205.
24
25 [34] K. Aparna, S. S. Krishnamurthy, M. Nethaji, P. Balaram, *Polyhedron* **1994**, *13*, 2993.
26
27 [35] Cambridge Crystallographic Data Centre, CCDC, 12 Union Road, Cambridge CB2
28 *1EZ, UK.*
29
30 [36] G. B. Deacon, T. Feng, P. C. Junk, B. W. Skelton, A. N. Sobolev, A. H. White, *Aust.*
31 *J. Chem.* **1998**, *51*, 75.
32
33 [37] B. Morosin, *J. Chem. Phys.* **1968**, *49*, 3007.
34
35 [38] M. Sturm, F. Brandl, D. Engel, W. Hoppe, *Acta Cryst. Sect. B* **1975**, *B31*, 2369.
36
37 [39] B. Chen, L. Wang, Y. Xiao, F. R. Fronczek, M. Xue, Y. Cui, G. Qian, *Angew. Chem.*
38 **2009**, *121*, 508; *Angew. Chem. Int. Ed.* **2009**, *48*, 500.
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Legends for Figures

Fig. 1 Simultaneous DTA/TG of ${}^3\infty[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ (**1**) reveals a five step release of 4,4'-bipyridine from the framework. The first three signals correspond to intercalated bipy equivalents, the fourth and fifth signal above 350 °C indicate the framework disassembly and reformation of the reagents.

Fig. 2 Simulated powder pattern (*I*) of ${}^3\infty[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ (from bottom to top) as well as powder diffractogram of the bulk product of the MOF formation (*2*) in comparison to diffractograms after disassembly of the MOF to LaCl_3 (*3*). Both reactions can be run in cycles as the repetitions of patterns indicate (MoK α_1 radiation, $\lambda = 0.7107 \text{ \AA}$).

Fig. 3 The double capped trigonal prismatic coordination sphere of N and Cl atoms around La^{III} in ${}^3\infty[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ as well as the thermal ellipsoids of the atoms reflecting 50% probability. Symmetry operations: I: 1-x, 2-y, 1-z, II: 2-x, 1-y, 1-z, III: 2-x, 2-y, 1-z, IV: -x, 2-y, 2-z.

Fig. 4 The crystal structure of ${}^3\infty[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ with a view along [001] (top) and [010] (bottom). Incorporated bipyridine molecules are either emphasized by ellipsoids (top) or omitted for clarity (bottom). La atoms are depicted as large grey balls, N atoms as dark, C atoms as well as Cl atoms as light grey balls. H atoms are omitted for clarity as well.

Fig. 5 Topological drawing of ${}^3\infty[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$ with a view along [100]. The framework can be identified with a three-dimensional (6,4)-net that consists of two two-dimensional 6,3-nets.

Scheme 1 The amine ligand 4,4'-bipyridine.

Table 1 Crystallographic Data for ${}^3[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$. Deviations are given in brackets.

formula	$\text{C}_{90} \text{H}_{72} \text{N}_{18} \text{La}_2 \text{Cl}_6$
formula weight	1896.18
crystal system	triclinic
space group	<i>P</i> -1
<i>a</i> / pm	1344.7(3)
<i>b</i> / pm	1371.5(3)
<i>c</i> / pm	1430.1(3)
α / °	79.48(3)
β / °	63.90(3)
γ / °	65.68(3)
<i>V</i> / (10 ⁶ pm ³)	2158.3(11)
<i>Z</i>	1
<i>d</i> _{calcd} / (g·cm ⁻³)	1.459
μ / cm ⁻¹	12.2
<i>T</i> / K	173(2)
data range	$3.18 \leq 2\theta \leq 54.66$
X-ray radiation / pm	Mo-K α , $\lambda = 71.073$
diffractometer	STOE Image Plate Diffraction System II
no. of unique reflections	9557
no. of refined parameters / refl./parameter ratio	567 / 17
R_1^a for <i>n</i> reflections with $F_o > 4\sigma(F_o)$; <i>n</i>	0.0447; 5743
R_1 (all)	0.0965
wR_2^b (all)	0.0951
remaining electron density (e/pm * 10 ⁶)	+0.85/-2.13 e/pm 10 ⁶

^a $R_1 = \sum [|F_o| - |F_c|] / \sum [|F_o|]$. ^b $wR_2 = (\sum w (F_o^2 - F_c^2)^2 / (\sum w (F_o^4)))^{1/2}$ [14].

Table 2 Selected Distances/pm and Angles/deg between Atoms of ${}^2_{\infty}[\text{La}_2\text{Cl}_6(\text{bipy})_5]\cdot 4\text{bipy}$.

Deviations are given in brackets.

atoms	distances	atoms	angles
La1 – N1	279.4(4)	N1 – La1 – N2	135.70(13)
La1 – N2	281.8(4)	N3 – La1 – N4	66.63(13)
La1 – N3	274.9(4)	Cl1 – La1 – Cl1 ^{#1}	68.05(5)
La1 – N4	276.4(4)	Cl2 – La1 – Cl3	102.49(5)
La1 – Cl1	288.7(2)	Cl1 – La1 – N3	98.00(10)
La1 – Cl1 ^{#1}	296.4(2)		
La1 – Cl2	276.0(2)		
La1 – Cl3	280.6(2)		

Symmetry operation: ^{#1} 1-x, 2-y, 1-z.

Fig. 1

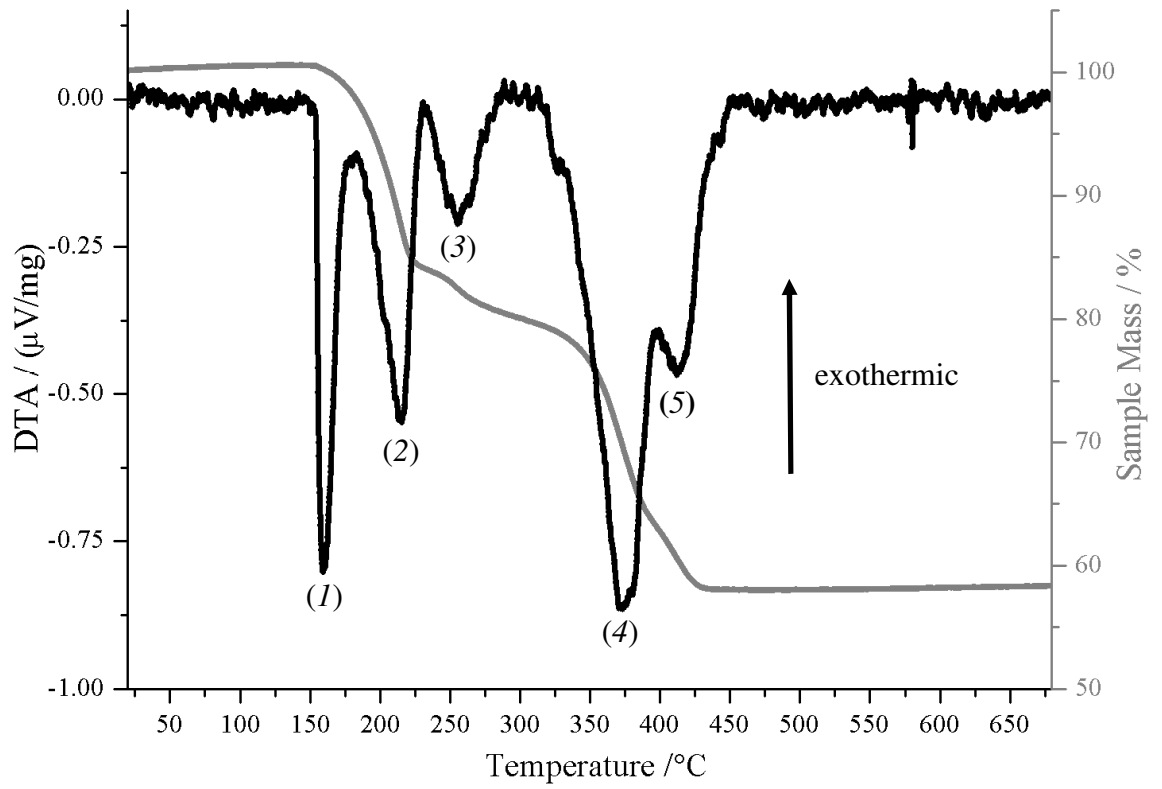


Fig. 2

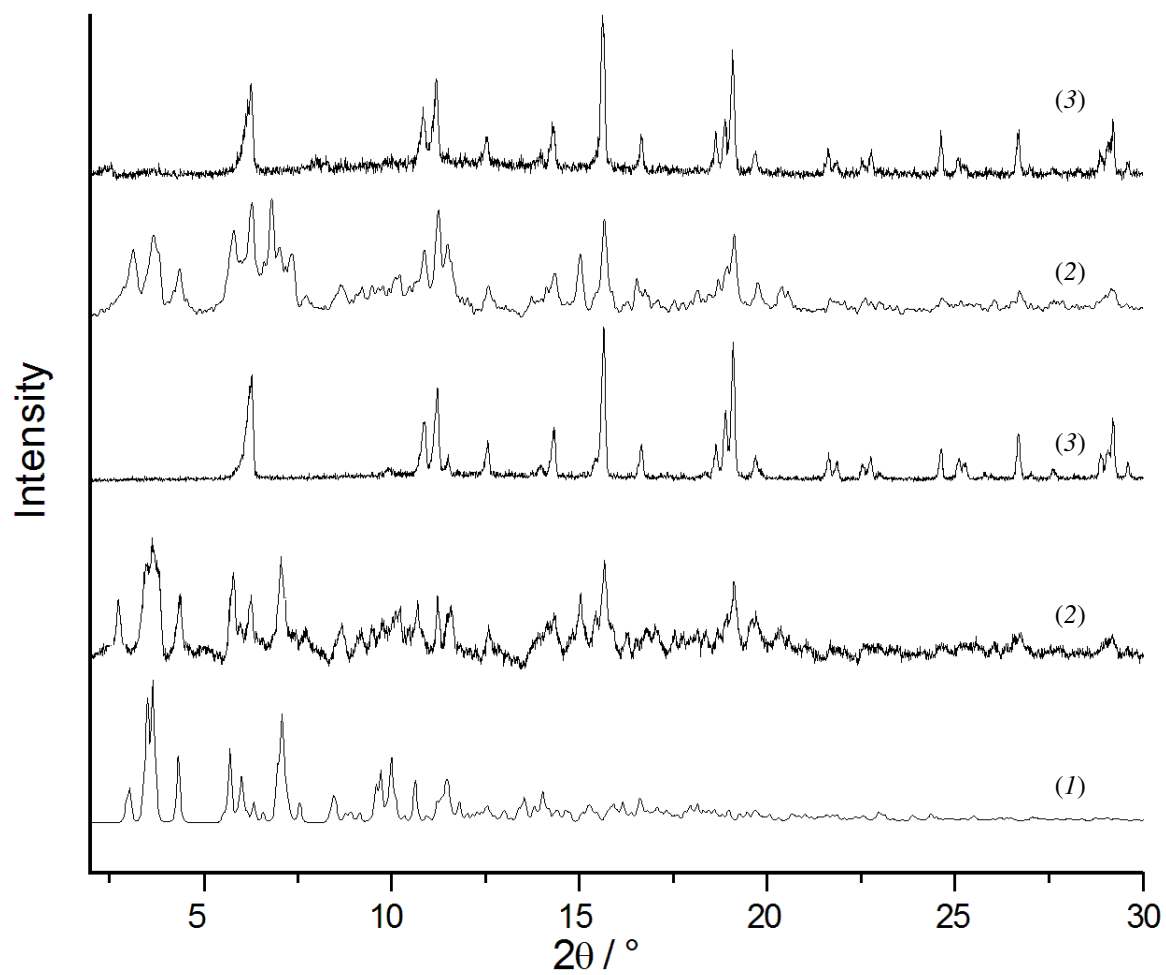


Fig. 3

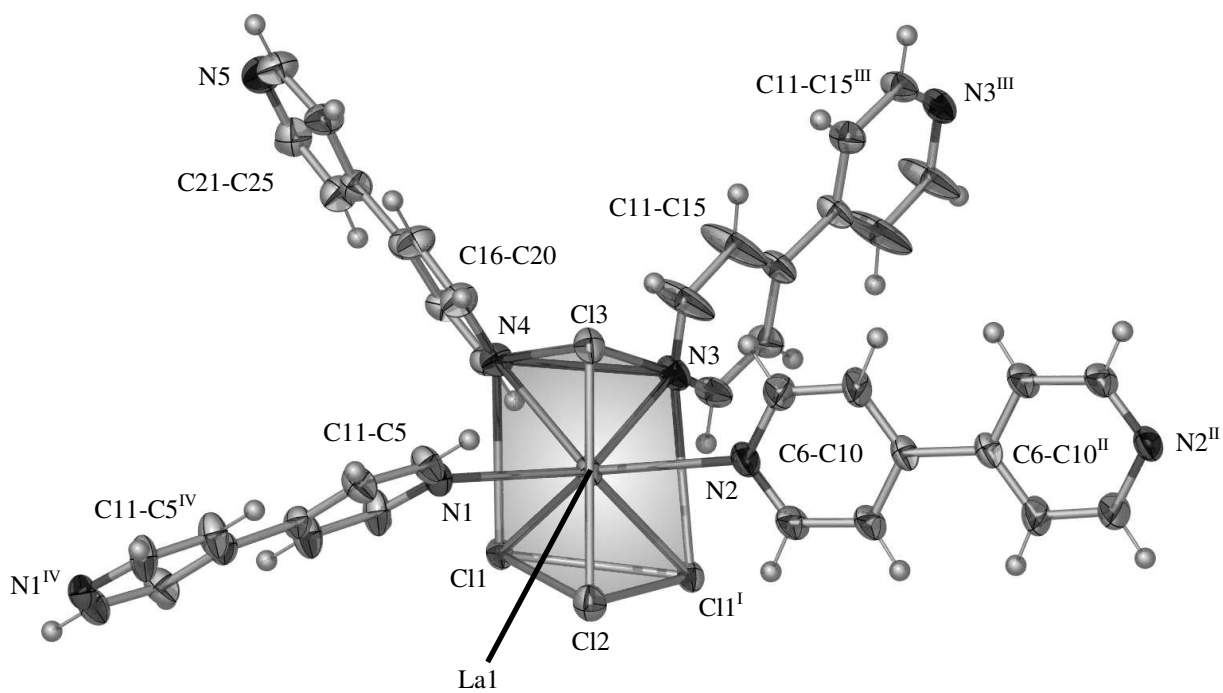


Fig. 4



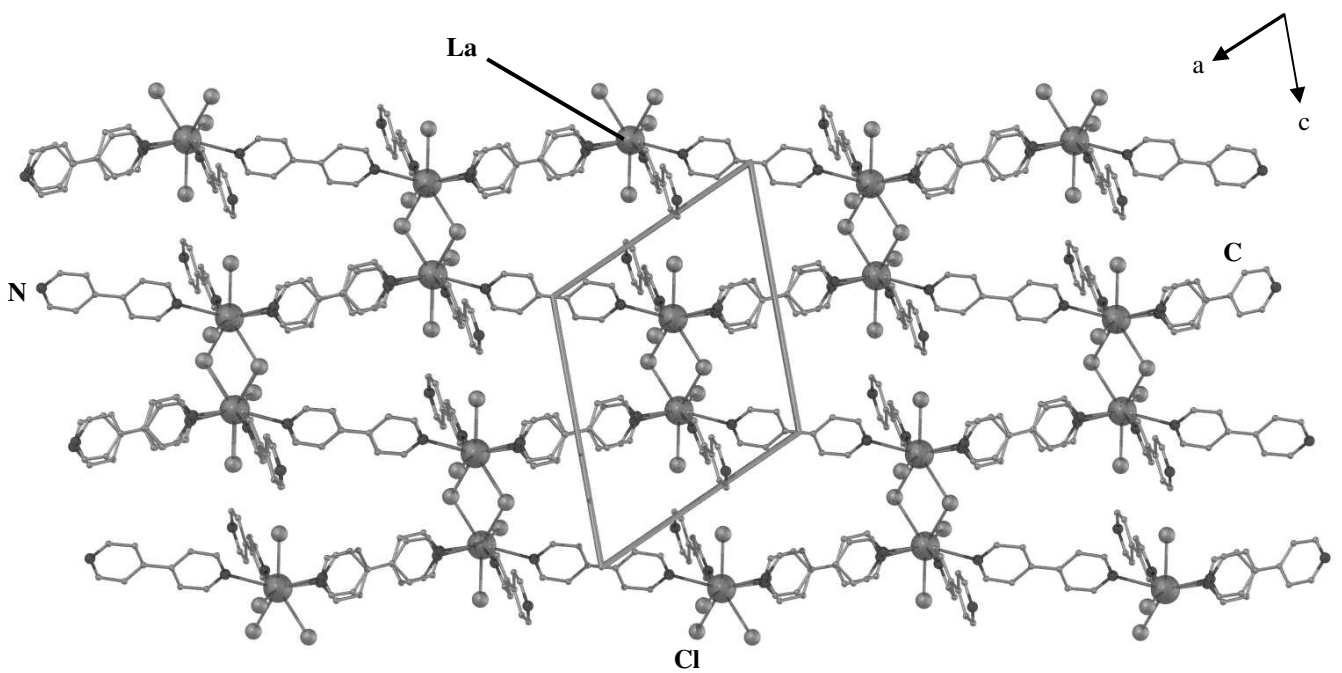


Fig. 5

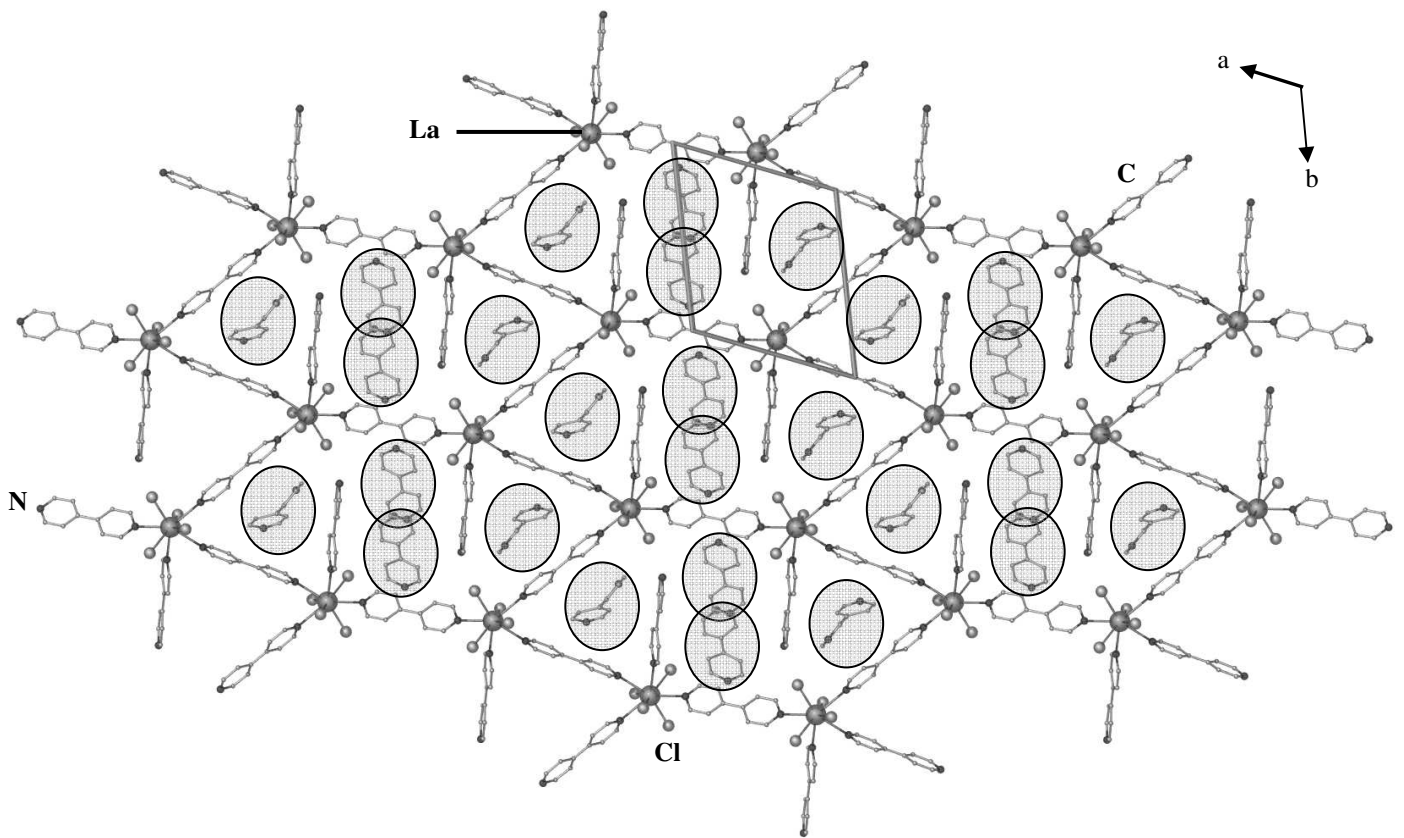

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Scheme 1

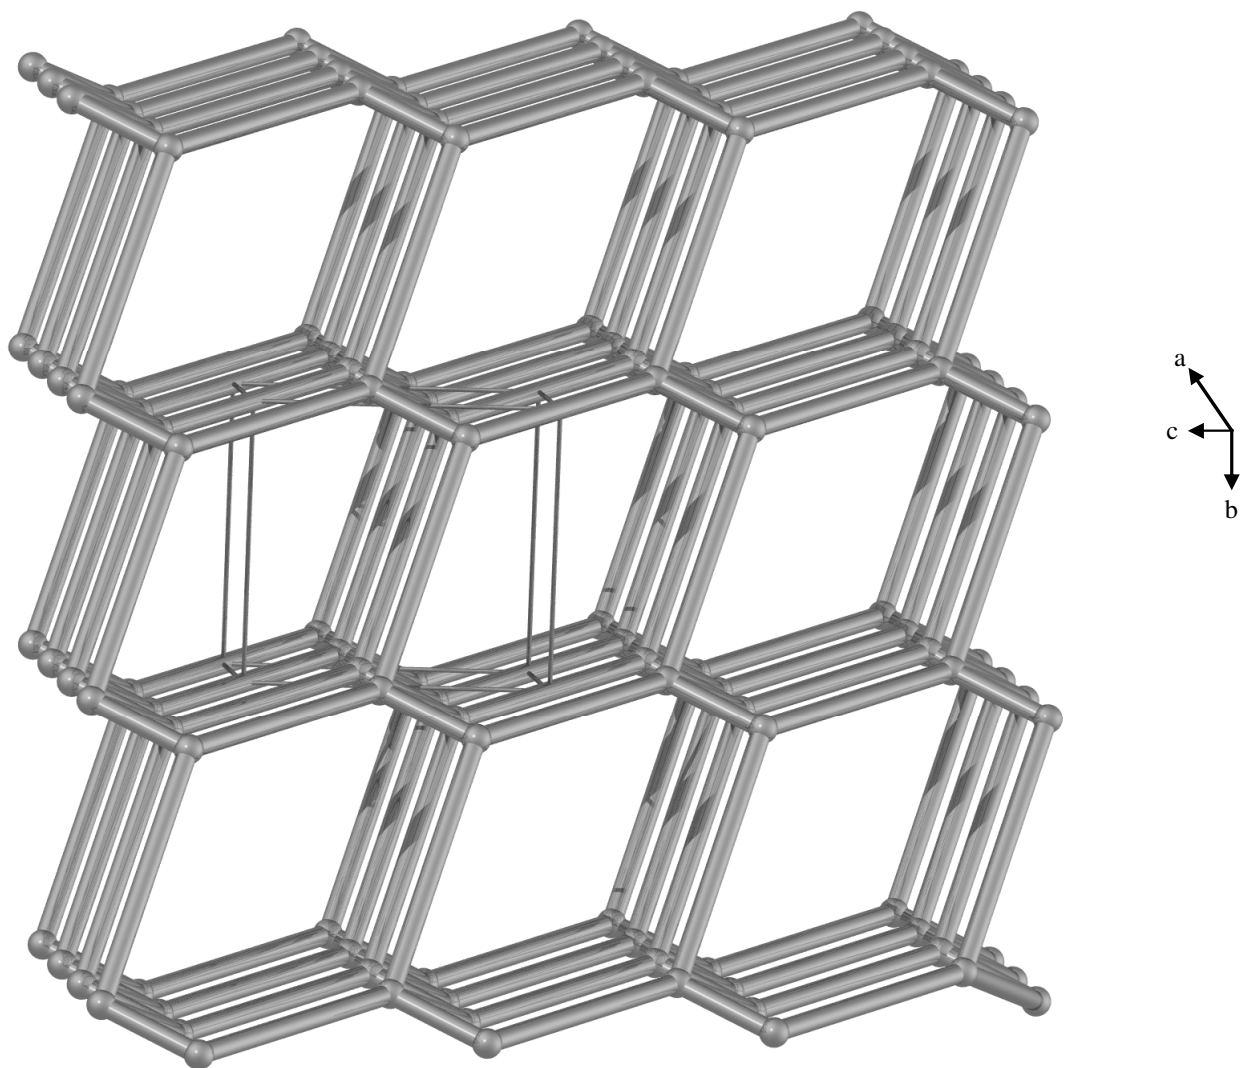