



**HAL**  
open science

## Automated Lab Scale Production of PVA/PEG-Enzyme Immobilisates

Nora C. Bieler, Marion Bettina Ansorge-Schumacher, Lasse Greiner

► **To cite this version:**

Nora C. Bieler, Marion Bettina Ansorge-Schumacher, Lasse Greiner. Automated Lab Scale Production of PVA/PEG-Enzyme Immobilisates. *Biotechnology Journal*, 2010, 5 (8), pp.881. 10.1002/biot.201000070 . hal-00552350

**HAL Id: hal-00552350**

**<https://hal.science/hal-00552350>**

Submitted on 6 Jan 2011

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



## Automated Lab Scale Production of PVA/PEG-Enzyme Immobilisates

|                               |  |
|-------------------------------|--|
| Journal:                      | <i>Biotechnology Journal</i>   |
| Manuscript ID:                | biot.201000070.R1  |
| Wiley - Manuscript type:      | Technical Report   |
| Date Submitted by the Author: | 30-Apr-2010  |
| Complete List of Authors:     | Bieler, Nora; Technical University of Berlin, Inst. of Chemistry, Dept. of Enzyme Technology (TC4)<br>Ansorge-Schumacher, Marion; Technical University of Berlin, Inst. of Chemistry, Dept. of Enzyme Technology (TC4)<br>Greiner, Lasse |
| Primary Keywords:             | Biocatalysis   |
| Secondary Keywords:           | Reaction Engineering   |
| Keywords:                     | immobilisation, automated production, Biotransformation  |
|                               |  |



## Technical Report

### Automated Lab Scale Production of PVA/PEG-Enzyme Immobilisates

Nora C. Bieler<sup>1</sup>, Marion B. Ansorge-Schumacher<sup>1</sup> and Lasse Greiner\*<sup>2,3</sup>

<sup>1</sup>Institute of Chemistry, Enzyme Technology, TU Berlin, Berlin, Germany

<sup>2</sup>Institut für Technische und Makromolekulare Chemie, RWTH Aachen University, Aachen, Germany

<sup>3</sup>DECHEMA e.V. Karl-Winnacker-Institut,, Frankfurt am Main, Germany

**Keywords:** immobilisation, polyvinyl alcohol, automated production, biocatalysis, entrapment

**Correspondence:** Lasse Greiner, Dr. rer. nat., Institut für Technische Chemie und Makromolekulare Chemie, RWTH Aachen University, Worringerweg 1, 52056 Aachen, Germany.

Email: [greiner@dechema.de](mailto:greiner@dechema.de), Tel.: +49 69 7564 428, Fax: +49 241 806 264 84

**Abbreviations:** **BAL**, benzaldehyde lyase, **SEM**, scanning electron microscopy,

**PVA**, polyvinyl alcohol, **PEG**, polyethylene glycol

1  
2  
3  
4  
5  
6 **Abstract.** Entrapment of biocatalysts by cryogelation is a gentle method to  
7  
8 extend the scope of biocatalysis. To foster the use of this versatile method we  
9  
10 devised an automated injector for the production of polyvinyl alcohol  
11  
12 (PVA)/polyethylene glycol (PEG) beads. The device consists of a thermostated  
13  
14 reservoir connected to a programmable injector nozzle and an agitated receiving  
15  
16 bath for the droplets. This lab scale production unit yields up to 1500 beads with  
17  
18 immobilised enzyme per minute with a narrow size distribution and good  
19  
20 roundness.  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

## 1 Introduction

In the field of biocatalysis the advantages of immobilised biocatalysts were early recognised and exploited [1, 2]. Recently, it could be shown that entrapment of biocatalysts in hydrogel beads allows stable operation in otherwise deteriorating solvents [3]. Therefore, matrix entrapment of biocatalysts in natural and synthetic polymers provides a means to overcome the limitations implied by the aqueous environment which a broad range of biocatalysts require for activity and stability [4].

As entrapment matrix PVA/PEG cryogels show a number of distinct advantages [5]. They exhibit high micro- and macroporosities resulting in high mass transfer rates and show a high stability towards a wide range of compounds. The shear resistance allows application in a broad range of reactor types, which makes PVA-cryogels superior over commonly used thermoreversible gels. Furthermore the starting material is non-toxic and readily available at reasonable costs.

Entrapment in PVA cryogels is a widely applied method for the immobilisation of whole cells, and has also been described for palladium catalysts [5, 6, 7]. As isolated enzymes benzaldehyde lyase from *Pseudomonas fluorescens* Biovar I. (EC 4.1.2.38), carbonyl reductase from *Candida parapsilosis* (EC 1.1.1.1), alcohol dehydrogenase from

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

*Lactobacillus kefir* (EC 1.1.1.2), and hog pancreas lipase (EC 3.1.1.3) have recently been entrapped and successfully applied to synthetic reactions in pure organic solvents [8, 9, 10]. Due to the mild entrapment conditions the activity yield was high even for sensitive enzymes. Generally, the stability towards organic solvents was increased by at least an order of magnitude.

PVA/PEG cryogels are most commonly applied as beads, because of the favourable hydrodynamics and abrasion stability in reactors. They are produced by cryogelation [11, 12, 13], i.e. a solution of PVA and PEG is added dropwise to silicone oil at 250 K, and gelation is induced by successive heating to room temperature [14]. Mostly, these are prepared manually. However, the highly viscous PVA/PEG solution gives rise to handling issues and large-scale production is prone to induce tenosynovitis when performed manually. The JetCutter as developed by Vorlop and coworkers was successfully employed for the production of enzyme immobilisates [15]. It is well suited for solutions with lower viscosity such as Ca-pectinate, Ca-alginate, Chitosan, gelatin and smaller bead diameters typically below 1 mm [15]. However, losses of 5-20% induced by the shear from the cutting are inevitable [16]. Lozinsky and coworkers hint towards an automated device as a Russian patent (as cited in ref. 12) apparently using pressure driven sheath flow to produce droplets but no quantitative data is accessible in literature. Again, in our experience the pressure drop over the nozzle in such setups is hard to predict or control, rising reproducibility issues.

1  
2  
3  
4  
5  
6 In this study, a device for the automated production of spherical PVA/PEG  
7  
8 cryogels for enzyme entrapment is presented. Evaluation was performed with  
9  
10 regard to immobilisation performance, reproducibility, bead shape and size,  
11  
12 as well as morphology of the resulting material.  
13  
14  
15  
16  
17

## 18 **2 Materials and Methods**

### 21 **Technical set up**

22  
23  
24 Micro-Liquid-Dispenser SMLD 300G was purchased from Fritz Gyger AG  
25  
26 (Thun-Gwatt, Switzerland). Electronical equipment was build by the  
27  
28 university workshops of RWTH Aachen University and TU Berlin. Wacker  
29  
30 AP 100 Silicone oil (Wacker Chemie AG, Burghausen, Germany) was used  
31  
32 as hardening solvent for PVA/PEG solution. An Ecoline Staredition RE300  
33  
34 thermostat with external temperature sensor from Lauda (Lauda-Königshofen,  
35  
36 Germany) with silicone oil M10 (Carl Roth, Karlsruhe, Germany) as coolant,  
37  
38 was used. The sample container was thermostated by a water bath (MgW  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
Lauda Thermo-star C3).

### 48 **Preparation of PVA/PEG solution**

50  
51 Polyvinyl alcohol Mowiol 10-98 (polymerisation degree: 1400) and  
52  
53 polyethylene glycol 1000 were purchased from Fluka (Neu-Ulm, Germany).  
54  
55 A mixture of 10% (w/v) PVA and 10% (w/v) PEG was dissolved in deionised  
56  
57  
58  
59  
60  
water at 90°C, 30 mg NaOH/g PVA was added at room temperature and the

1  
2  
3  
4  
5  
6 solution was stirred for 30 minutes to cleave ester residues in the commercial  
7  
8 PVA solution. The pH was adjusted to 8.0 with concentrated HCl [8].  
9

### 10 **PVA bead analysis**

11  
12 For analysis of size distribution PVA beads were removed from the silicone  
13  
14 oil bath, washed with distilled water and sieved (ISO 3310/1, Retsch, Haan,  
15  
16 Germany). Size exclusions in sieve analysis were 5.00, 4.00, 3.55, 3.15, 2.50,  
17  
18 2.00, 1.40, 1.00, 0.80, 0.60, 0.50, 0.40, 0.30 and 0.10 mm.  
19  
20  
21  
22

23  
24 For shape analysis PVA beads were prepared by dyeing with ethanol/aqueous  
25  
26 solution (20%, (v/v)) of 0.1% (w/v) Bromocresol green for 30 seconds. A  
27  
28 digital picture (Olympus SP-500UZ) was converted to greyscale with  
29  
30 maximum contrast via GIMP (Version 2). The pictures were subsequently  
31  
32 analysed for bead roundness with the software Image Tool® (Version 3.0).  
33  
34 The bead shape was described by roundness and compactness. Roundness is  
35  
36 defined as  $(4*\pi*area)/perimeter^2$  where perimeter is the length of the outside  
37  
38 boundary of the object. Compactness is given by  $(4*area/\pi)^{1/2}/major\ axis$   
39  
40 length. Both parameters are the closer to unity the rounder or closer to ideal  
41  
42 circular the object is.  
43  
44  
45  
46  
47

48 For scanning electron microscopy (SEM) PVA beads were prepared by shock  
49  
50 freezing in liquid nitrogen and freeze drying (Alpha 1-2 LD plus, Christ,  
51  
52 Riedstadt, Germany). SEM was conducted using a Hitachi S-2700 instrument  
53  
54 at an acceleration voltage of 20 kV. Samples were fixed on double-sided  
55  
56 adhesive foils and sputtered with thin gold films.  
57  
58  
59  
60

### Activity assay

Benzaldehyde lyase (BAL) from *Pseudomonas fluorescens* Biovar I [E.C.4.1.2.38] was expressed and purified using the recombinant *E. coli* SG13009<sub>prep4</sub> [pBAL-his<sub>6</sub>] as described previously [17]. In the PVA/PEG solution lyophilised BAL (0.5 U mL<sup>-1</sup>), thiamine diphosphate (0.1 mmol L<sup>-1</sup>), and MgSO<sub>4</sub> (2.5 mmol L<sup>-1</sup>) were dissolved [8]. The activity of BAL immobilised in PVA/PEG beads was determined by monitoring the BAL-catalysed carbologation of benzaldehyde to benzoin by gas chromatography (Shimadzu 2010 using a BTX column from SGE). Reactions were performed at 303 K in closed glass vessels containing 17 g of immobilisates and 10 mL of 200 mM benzaldehyde (Sigma-Aldrich, Steinheim, Germany) in *tert*-butyl methyl ether (Carl Roth, Karlsruhe, Germany).

## 3 Results

### Set up

It was aimed for a device which would give spherical beads with narrow size distribution. Besides, thermal stress on the enzyme should be reduced to minimum. Also the influence of temperature on the cryogelation process was target of our investigations both the storage temperature and the bath temperature should be varied. The overall setup consists of the dosing unit and a thermostated bath.

1  
2  
3  
4  
5  
6 The dosing unit is a double jacket tube (50 mL inner volume) with top side  
7  
8 connection for either compressed air or nitrogen. The outlet consists of a  
9  
10 commercially available microvalve which was embedded into an electrically  
11  
12 heated block allowing dosage of viscous solutions at low pressures.  
13  
14 Temperature and valve parameters were controlled electronically. Typically,  
15  
16 the PVA/PEG enzyme solutions were transferred to the tube and pressurised  
17  
18 to 5 kPa with nitrogen. The scheme of the dosing unit is shown in figure 1.  
19  
20 For the investigated system the injection temperature could be kept at room  
21  
22 temperature. Thereby, thermal stress of the enzyme was minimised.  
23  
24  
25

26  
27 The outlet of the valve was directed into a double jacket insulated silicone oil  
28  
29 bath. Circulation in the receiving bath was maintained by a stirrer. The bath  
30  
31 layout prevented the agglomeration of beads by coalescence of droplets. The  
32  
33 distance from the valve outlet to the bath surface was adjusted to give  
34  
35 spherical beads. Too short distances lead to the distortion of shape and a  
36  
37 distance of 20 cm was found to give best results (Figure 1).  
38  
39  
40

41  
42 The PVA/PEG enzyme solution was injected into the receiving bath at 248 K.  
43  
44 The frozen beads were collected into a dent of the bath by the induced flow.  
45  
46 After the injection process the temperature was increased to 298 K over  
47  
48 500 minutes [18, 19]. Shortening to 180 minutes led to PVA beads with no  
49  
50 apparent differences in stability, flexibility, and porosity. Higher initial  
51  
52 temperatures of 268 K for the receiving bath were tested in accordance with  
53  
54 literature [12, 20]. The obtained beads showed deviations from spherical  
55  
56  
57  
58  
59  
60

1  
2  
3  
4  
5  
6 shape, presumably because freezing time is prolonged, so that beads were  
7  
8 deformed by the stirrer.  
9

### 10 **Bead size and shape**

11  
12 Size of PVA/PEG beads is a function of opening and closing times of the  
13  
14 valve. We tested three time programs at 20 ms, 40 ms, and 60 ms opening  
15  
16 times with 20 ms, 25 ms, and 30 ms pause, respectively (Figure 2). This  
17  
18 theoretically equates to 25, 15, and 11 beads per second allowing the  
19  
20 formation of beads needed for a typical lab scale continuous fluidised bed  
21  
22 reactor within minutes [21].  
23  
24  
25  
26  
27

28 With 60 ms 47% of all obtained beads were within 2.5 to 3.15 mm in  
29  
30 diameter correlating to 73% of the total mass. 83% of the mass of the beads  
31  
32 were contained within 2.5 and 3.55 mm. At 40 ms smaller PVA beads with  
33  
34 80% of all the produced beads within a diameter of 2.0 to 2.5 mm were  
35  
36 obtained. 72% of the beads showed a diameter of 2.5 mm. The shortest tested  
37  
38 impulse length of 20 ms led to a size distribution of PVA immobilisates  
39  
40 where 83% had a diameter between 1.4 and 2 mm. 88% of all these beads  
41  
42 were ranged in size between 1 and 2 mm. On average the yield of beads per  
43  
44 mass was around 75% and is due to losses in the storage vessel and at the  
45  
46 nozzle.  
47  
48  
49  
50

51  
52 So far, the production of beads is only limited by clogging after time which  
53  
54 occurs as a result of gelation taking place at the nozzle. As the gelation  
55  
56 process is envisaged to be induced by local high concentrations of PVA  
57  
58  
59  
60

1  
2  
3  
4  
5 during the thawing process favouring the formation of hydrogen bonds [13]  
6  
7  
8 the reason for this gel formation at the nozzle is unclear. Here, deeper  
9  
10 understanding of the gelation process as well as the probable role of wetted  
11  
12 materials in the nozzle is needed for further improvement.  
13  
14  
15 Besides the size distribution roundness is an issue for mass transfer and  
16  
17 robustness [22]. Bead shape analysis was performed for four bead batches. As  
18  
19 indicator for a perfectly round shape roundness =  $(4 \pi \text{ area} / \text{perimeter}^2)$  and  
20  
21 compactness =  $(4 \text{ area} / \pi)^{1/2}$  major axis length can be applied. Both indicators  
22  
23 approach unity for ideal spheres. An average roundness of  $0.85 \pm 0.03$  was  
24  
25 determined. Compactness was determined as  $0.95 \pm 0.02$ . Both parameters  
26  
27 indicate a close spherical shape of the beads.  
28  
29  
30  
31  
32

### 33 **Gel morphology**

34  
35 The structure and the pore size of the PVA/PEG cryogels resulting from the  
36  
37 automated production were determined via scanning electron microscopy  
38  
39 (SEM) (Figure 3). Typical sponge structure and pore sizes around  $1 \mu\text{m}$  are in  
40  
41 line with previously obtained results [23]. In contrast to manually produced  
42  
43 PVA beads gas inclusions of varying sizes were observed in 80% of the  
44  
45 beads.  
46  
47  
48  
49

50  
51 However, the activity tests with entrapped BAL showed within the error  
52  
53 margin the same activity and storage stability as the manually produced  
54  
55 beads. Typically a productivity of  $40 \mu\text{mole h}^{-1}$  per immobilised U of BAL  
56  
57 were obtained.  
58  
59  
60

#### 4 Conclusion

We set up a means for standardised automated PVA/PEG immobilisate lab scale production. Our method achieves high productivity of up to 1500 beads per minute. The size distribution of the PVA beads is narrow and the diameter can be varied by the valve pulse interval. The obtained beads are spherically shaped and robust allowing the use in a range of reactor configurations. Temperature stress during production of PVA/PEG immobilisates is low as temperatures are at or below room temperature. Furthermore the presented set up for automated bead production is straightforward and the additional costs are low. The used liquid dispenser is readily available. Our design for routine lab-scale production of beads now enables application of these promising immobilisates in larger scale.

#### Acknowledgments

The work was funded by the Deutsche Forschungsgemeinschaft via the GRK 1166 BioNoCo ([www.bionoco.org](http://www.bionoco.org)) and the Clusters of Excellence TMFB (RWTH Aachen University) and UniCat (TU Berlin). We thank Peter Hochstenbach from the university workshop of RWTH Aachen University, Rolf Kunert, Michael Knuth and Axel Schiele from the university workshop of TU Berlin for technical assistance and discussion.

The authors have declared no conflict of interest.

## 5 References

- [1] End, N., Schöning, K.-U., Immobilized Biocatalysts in Industrial Research and Production, in: Topics in Current Chemistry, *Immobilized Catalysts*, Springer Verlag, Berlin Heidelberg 2004, 242, pp. 273-317.
- [2] Lalonde, J., Margolin, A., Immobilization of Enzymes, in: Drauz, K., Waldmann, H. (Ed.), *Enzyme Catalysis in Organic Synthesis*, Wiley-VCH Verlag, Weinheim 2002, pp. 163-184.
- [3] Ansorge-Schumacher, M. B., Two-Phase Systems with Solidified Water Phases – Tools for Technical Use of Sensitive Catalysts. *Mini-Reviews in Organic Chemistry* 2007, 4, 243-245.
- [4] Carrea, G., Riva, S., Properties and synthetic applications of enzymes in organic solvents. *Angew. Chem. Int. Ed. Engl.* 2000, 39, 2226-2254.
- [5] Lozinsky, V. I., Plieva, F. M., Poly(vinyl alcohol) cryogels employed as matrices for cell immobilization. 3. Overview of recent research and developments. *Enzyme Microb. Technol.* 1998, 23, 227-242.
- [6] Szczesna, M., Galas, E., *Bacillus subtilis* cells immobilised in PVA-cryogels. *Biomolecular Eng.* 2001, 17, 55-63.
- [7] Prüsse, U., Hörold, S., Vorlop, K.-D., Verkapselung mikroskopischer Katalysatoren in gelförmigen Polymernetzwerken. *Chemie Ingenieur Technik* 1997, 69, 100-103.
- [8] Hischer, T., Steinsiek, S., Ansorge-Schumacher, M. B., Use of polyvinyl alcohol cryogels for the compartmentation of biocatalysed reactions in non-aqueous media. *Biocatal. Biotransformation* 2006, 24, 437-442.
- [9] Metrangolo-Ruiz De Temiño, D., Hartmeier, W., Ansorge-Schumacher, M. B., Entrapment of the alcohol dehydrogenase from *Lactobacillus kefir* in polyvinyl alcohol for the synthesis of chiral hydrophobic alcohols in organic solvents. *Enzyme Microb. Technol.* 2005, 36, 3-9.
- [10] Plieva, F. M., Kochetkov, K. A., Singh, I., Parmar, V. S., Belokon, Y. N., Lozinsky, V.I., Immobilization of hog pancreas lipase in macroporous poly(vinyl alcohol)-cryogel carrier for the biocatalysis in water-poor media. *Biotechnol. Lett.* 2000, 22, 551-554.
- [11] Lozinsky, V. I., Damshkaln, L. G., Kurochkin, I. N., Kurochkin, I. I., Study of cryostructuring of polymer systems: 28. Physicochemical properties and morphology of poly(vinyl alcohol) cryogels formed by multiple freezing-thawing. *Colloid Journal* 2008, 70, 189-198.
- [12] Lozinsky, V. I., Solodova, E. V., Zubov, A. L., Simenel, I. A., Study of Cryostructuring of Polymer Systems. XI. The Formation of PVA Cryogels by Freezing-Thawing the Polymer Aqueous Solution Containing Additives of some Polyols. *J Appl Polym Sci* 1995, 58, 171-177.


- 1  
2  
3  
4  
5  
6 [13] Lozinsky, V. I., Cryotropic gelation of poly(vinyl alcohol) solutions. *Russ Chem Rev* 1998, *67*, 573-586.  
7  
8  
9 [14] Prüße, U., Entwicklung, Charakterisierung und Einsatz von  
10 Edelmetallkatalysatoren zur Nitratreduktion mit Wasserstoff und Ameisensäure  
11 sowie des Strahlschneider-Verfahrens zur Herstellung Polyvinylalkohol-  
12 verkapselter Katalysatoren. *Landbauforschung Völkenrode* 2000, Sonderheft  
13 214.  
14  
15 [15] Prüße, U., Dalluhn, J., Breford, J., Vorlop, K.-D., Production of Spherical  
16 Beads by JetCutting. *Chem. Eng. Technol.* 2000, *23*, 1105-1110.  
17  
18 [16] Prüße, U., Bruske, F., Vorlop, K.-D., Improvement of the Jet Cutting  
19 Method for the Preparation of Spherical Particles from Viscous Polymer  
20 Solutions. *Chem. Eng. Technol.*, 1998, *21*, 153-157.  
21  
22 [17] Janzen, E., Müller, M., Kolter-Jung, D., Kneen, M. M. *et al.*,  
23 Characterization of benzaldehyde lyase from *Pseudomonas fluorescens*: A  
24 versatile enzyme for asymmetric C-C bond formation. *Bioorg. Chem.* 2006, *34*,  
25 345-361.  
26  
27 [18] Lozinsky, V. I., Cryogels on the basis of natural and synthetic polymers:  
28 preparation, properties and applications. *Russ. Chem Rev* 2002, *71*, 489-511.  
29  
30 [19] Mikhalev, O. I., Sierpinski, M., Lozinsky, V. I., Kapanin, P. V. *et al.*,  
31 Method for determination of liquid microphase volume: application to the  
32 investigation of frozen H<sub>2</sub>O-poly(vinyl alcohol) system. *Cryo-Lett* 1991, *12*,  
33 197-206.  
34  
35 [20] Leidig, E., Prüße, U., Vorlop, K. D., Winter, J., Biotransformation of poly  
36 R-478 by continuous cultures of PVAL-encapsulated *Trametes versicolor* under  
37 non-sterile conditions. *Bioproc Eng* 1999, *21*, 5-12.  
38  
39 [21] Ansorge-Schumacher, M. B., Greiner, L., Schroeper, F., Mirtschin, S. *et al.*,  
40 Operational concept for the improved synthesis of (*R*)-3,3'-furoin and related  
41 hydrophobic compounds with benzaldehyde lyase. *Biotechnol J* 2006, *1*, 564-  
42 568.  
43  
44 [22] Buthe, A., Hartmeier, W., Ansorge-Schumacher, M. B., Novel solvent-based  
45 method for preparation of alginate beads with improved roundness and  
46 predictable size. *J. Microencapsulation* 2004, *21*, 865-876.  
47  
48 [23] Lozinsky, V. I., Vainerman, E. S., Domotenko, L. V., Mamtsis, A. M. *et al.*,  
49 Study of cryostructurization of polymer systems VII. Structure formation under  
50 freezing of poly(vinyl alcohol) aqueous solutions. *Colloid Polym Sci* 1986, *264*,  
51 19-24.  
52  
53  
54  
55  
56  
57  
58  
59  
60

## Figure legends


**Figure 1.** Setup of the apparatus, right: dosing unit with electronic valve (EV) and thermostated storage for the enzyme solution (ES); middle left: photograph of the injection module; lower left: top view of the receiving bath with flow direction and drop point (DP) (dimensions in mm, KF: flange with O-ring, P: manometer, S: stirrer, TJ; thermostated jacket, TB: thermoblock).

**Figure 2.** Size distribution of automatically produced PVA/PEG immobilisates as a function of valve opening time (open spheres) 60 ms, (closed diamonds) 40 ms and (open triangles) 20 ms.


**Figure 3.** SEM images of beads (A) surface, (B-D) cross sections with increasing magnification, (E+F) surface and cross section of a bead with gas entrapment.

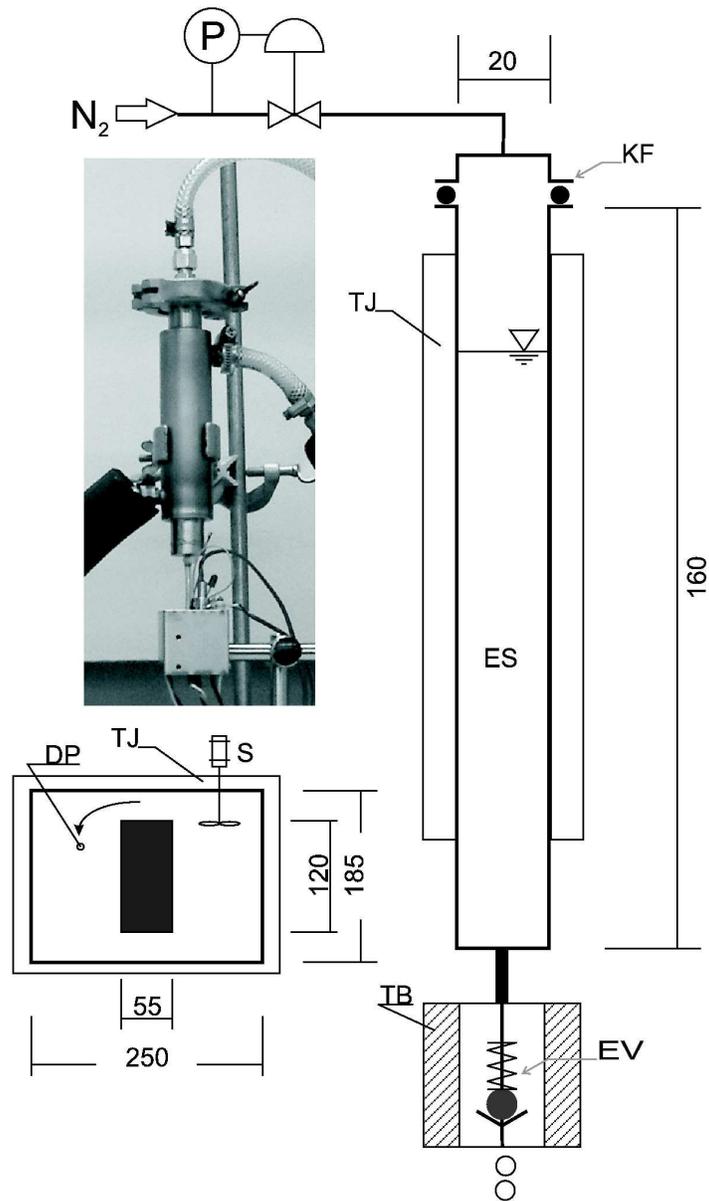

Setup of the apparatus, right: dosing unit with electronic valve (EV) and thermostated storage for the enzyme solution (ES); middle left: photograph of the injection module; lower left: top view of the receiving bath with flow direction and drop point (DP) (dimensions in mm, KF: flange with O-ring, P: manometer, S: stirrer, TJ: thermostated jacket, TB: thermoblock).  
150x257mm (600 x 600 DPI)

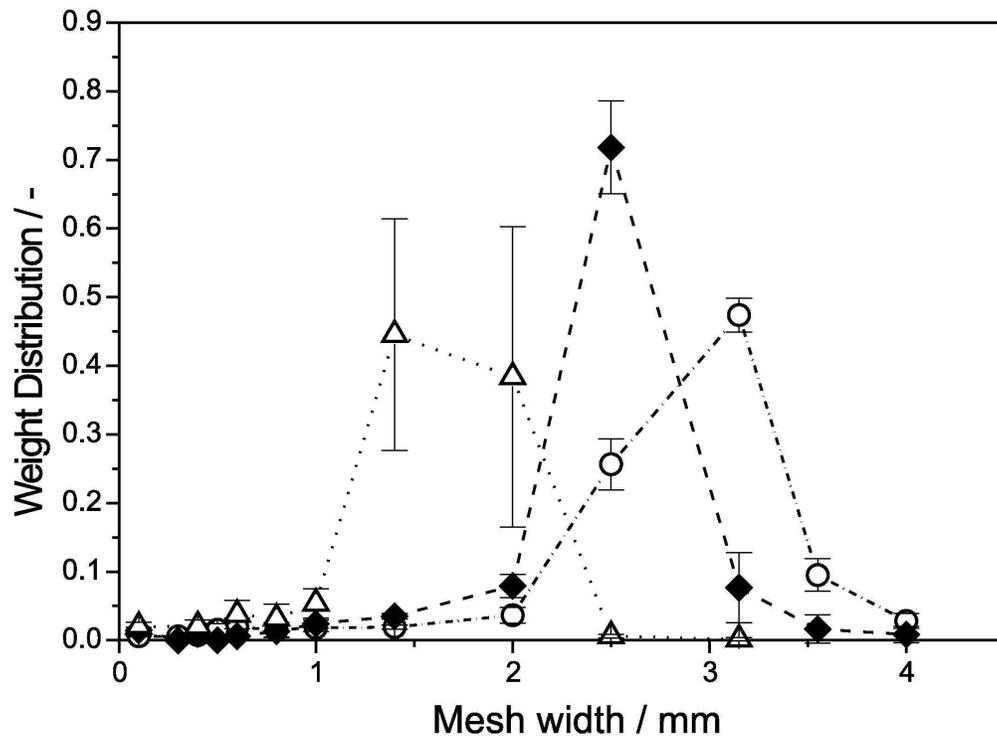

Size distribution of automatically produced PVA/PEG immobilisates as a function of valve opening time (open spheres) 60 ms, (closed diamonds) 40 ms and (open triangles) 20 ms.  
90x68mm (600 x 600 DPI)

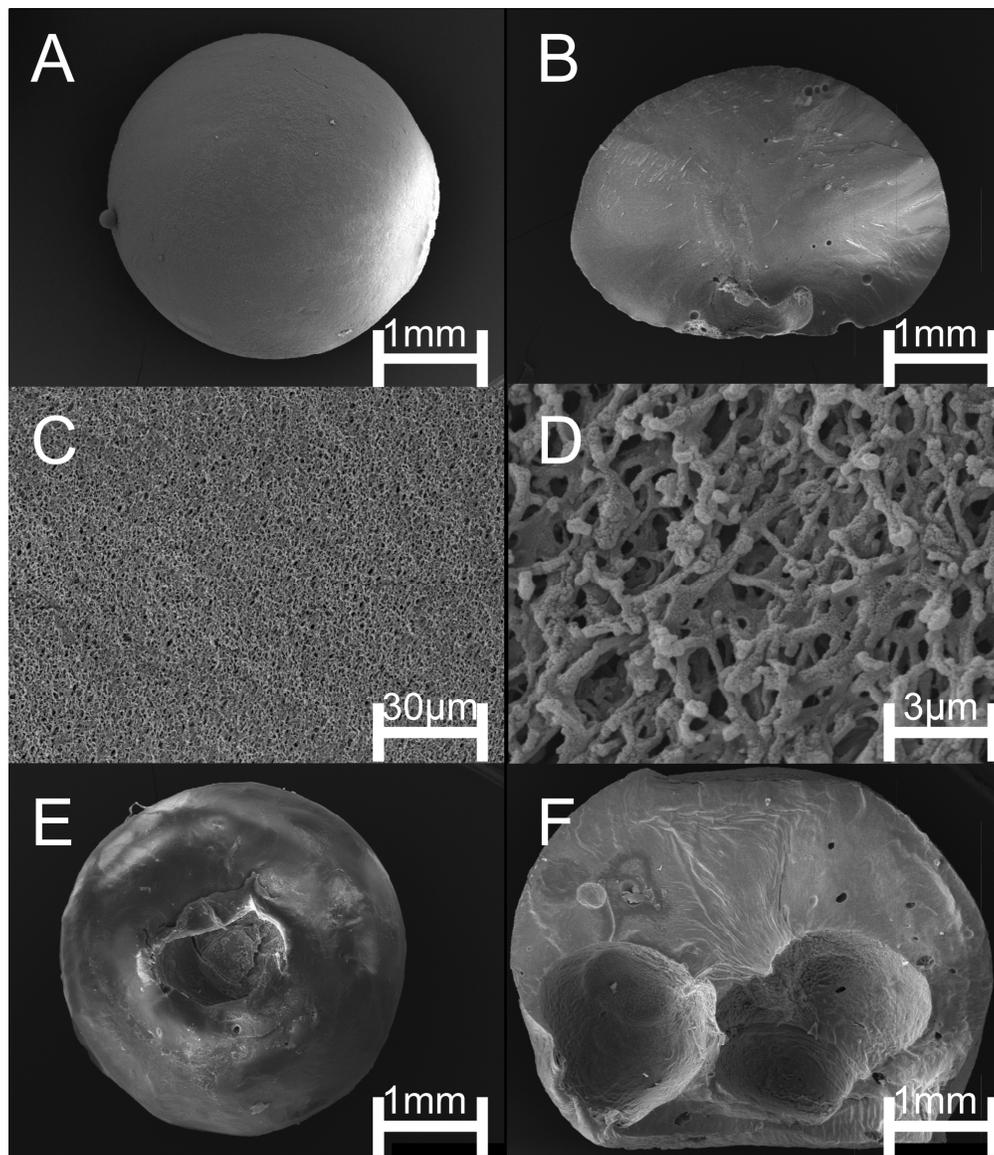

SEM images of beads (A) surface, (B-D) cross sections with increasing magnification, (E+F) surface and cross section of a bead with gas entrapment.  
123x142mm (600 x 600 DPI)