



**HAL**  
open science

## Lanthanide containing ionic liquid crystals: EuBr<sub>2</sub>, SmBr<sub>3</sub>, TbBr<sub>3</sub> and DyBr<sub>3</sub> in C<sub>12</sub>mimBr

Anja-Verena Mudring

► **To cite this version:**

Anja-Verena Mudring. Lanthanide containing ionic liquid crystals: EuBr<sub>2</sub>, SmBr<sub>3</sub>, TbBr<sub>3</sub> and DyBr<sub>3</sub> in C<sub>12</sub>mimBr. *Journal of Inorganic and General Chemistry / Zeitschrift für anorganische und allgemeine Chemie*, 2010, 636 (9-10), pp.1726. 10.1002/zaac.201000070 . hal-00552457

**HAL Id: hal-00552457**

**<https://hal.science/hal-00552457>**

Submitted on 6 Jan 2011

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

**Lanthanide containing ionic liquid crystals: EuBr<sub>2</sub>, SmBr<sub>3</sub>,  
TbBr<sub>3</sub> and DyBr<sub>3</sub> in C<sub>12</sub>mimBr**

Journal:	<i>Zeitschrift für Anorganische und Allgemeine Chemie</i>
Manuscript ID:	zaac.201000070.R1
Wiley - Manuscript type:	Article
Date Submitted by the Author:	14-Mar-2010
Complete List of Authors:	Mudring, Anja-Verena; Ruhr-Universitaet Bochum, Anorganische Chemie I
Keywords:	Ionic Liquids, Liquid Crystals, Luminescence, Lanthanides



DOI: 10.1002/zaac.2008

# Lanthanide containing ionic liquid crystals: $\text{EuBr}_2$ , $\text{SmBr}_3$ , $\text{TbBr}_3$ and $\text{DyBr}_3$ in $\text{C}_{12}\text{mimBr}$

Anna Getsis and Anja-Verena Mudring\*

Bochum, Fakultät für Chemie und Biochemie, Anorganische Chemie I, Festkörperchemie und Materialien,  
Ruhr-Universität Bochum

Received

*Dedicated to Professor Bernd Harbrecht on the Occasion of his 60<sup>th</sup> Birthday.*

**Abstract.** Doping the ionic liquid crystal  $\text{C}_{12}\text{mimBr}$  with various lanthanide halides yields interesting novel liquid crystalline and luminescent materials. The thermal phase behavior of all compounds was investigated by hot-stage polarizing optical microscopy and differential scanning calorimetry and the photophysical properties were determined by luminescence spectroscopy.  $\text{C}_{12}\text{mimBr}$  itself is an ionic liquid crystal that shows bluish-white emission upon excitation with UV light due to transitions in the imidazolium  $\pi$ -system. Doping lanthanide bromides into  $\text{C}_{12}\text{mimBr}$  with concentrations of about 1 mol% does not affect the liquid crystalline behaviour of the host materials to a great extent and room temperature liquid crystals are obtained. All

materials show an appreciable luminescence.  $\text{EuBr}_2$  in  $\text{C}_{12}\text{mimBr}$  yields a material which shows a blue emission originating from 4f-5d-transitions.  $\text{SmBr}_3$ -doped samples show a red and  $\text{TbBr}_3$  samples a green luminescence. Upon doping  $\text{C}_{12}\text{mimBr}$  with  $\text{DyBr}_3$  an orange luminescent liquid crystalline material is obtained. Most interestingly the emission color for the  $\text{TbBr}_3$  and  $\text{DyBr}_3$  containing materials can be tuned from bluish-white (mainly  $\text{C}_{12}\text{mimBr}$  emission) to green (for  $\text{TbBr}_3$ ) and orange-yellow (for  $\text{DyBr}_3$ ) depending on the wavelength of the excitation light used.

**Keywords:** Dysprosium; Europium; Ionic Liquid; Liquid Crystal; Luminescence; Samarium; Terbium

## Introduction

Although ionic liquids (ILs) have received an exceptionally high attention as a new class of solvents and materials for various applications, the understanding of interactions within these liquids is still rather limited. It has been noted from early on that ILs are highly structured liquids<sup>1</sup>. Ionic liquid crystals (ILCs) represent a special class of ILs where weak hydrophobic interactions of alkyl groups, dipole-dipole, cation- $\pi$  interactions as well as  $\pi$ - $\pi$  stacking of the commonly used aromatic head groups of the cation such as imidazolium or pyridinium as well as ionic interactions are tremendously important and are the driving force for the formation of ordered liquids, hence, liquid crystalline phases.

The liquid crystalline state of matter shows characteristics which are intermediate between that of a three-dimensionally well ordered crystalline solid and an isotropic liquid where the constituents are distributed randomly through space.<sup>2</sup>

\*Prof. Dr. Anja-Verena Mudring  
Ruhr-Universität Bochum, Fakultät für Chemie und Biochemie; Anorganische Chemie I – Festkörperchemie und Materialien  
D-44780 Bochum  
www.anjamudring.de

Generally, in the liquid crystalline state a random distribution of particles - like in a classical liquid - is observed at least in one direction of space whereas in another direction a substantially higher degree of order is observed which comes close to the periodicity of crystalline materials. Typically, many of the physicochemical properties of liquid crystals (LCs) such as refractive index, electric permittivity, magnetic susceptibility, and mechanical properties like viscosities are highly dependent on the direction in which these properties are measured. This has shown to be useful for a wide variety of applications and, in consequence, molecular liquid crystalline materials have found widespread applications in display technology in laptops, mobile phones, or flat screen television sets.<sup>3</sup>

Whilst most known liquid crystals are neutral molecular organic compounds of strong anisotropic shape, ionic liquid crystals (ILCs) are constituted of anions and cations. Mesophasic behaviour can be introduced into such an ionic material via either one of the ions. It is known that 1-alkyl-3-methylimidazolium salts with twelve and more carbon atoms in the side chain adopt mesophases and that the mesophase stability rapidly increases with increase in the alkyl chain length<sup>4</sup>. Most times, a lamellar mesophase, a smectic A phase or other highly ordered smectic phases are observed. It has been realized that ILCs show unique characteristics that cannot be observed in conventional molecular LCs. In ILCs a

1 tetragonal smectic phase  $S_T$  was observed for the first time.<sup>5</sup>  
 2 Recently, it was shown that double alkyl substituted  
 3 imidazolium ILCs show strong non-Newtonian fluidic  
 4 behavior in the LC state while they are Newtonian liquids in  
 5 the liquid IL state.<sup>6</sup> ILCs also show a strong tendency for  
 6 spontaneous homeotropic alignment.<sup>7</sup> Applications of ionic  
 7 liquid crystals are, so far, as ion-conductive materials,  
 8 organized reaction media or self-assembled nanostructured  
 9 materials.<sup>8</sup>

10 Metal-containing liquid crystals (metallomesogens)  
 11 form a special class of ILCs. By choosing a suitable metal ion  
 12 as the ILC constituent additional functionalities that origin  
 13 from the metals such as redoxactivity, magnetism or  
 14 luminescence can be introduced into the material. In  
 15 consequence, multifunctional materials are obtained. Several  
 16 reviews survey the intensive studies on neutral, uncharged  
 17 metallomesogens.<sup>9</sup> In contrast studies of ionic  
 18 metallomesogens have been neglected until recently<sup>10,11</sup>.  
 19 Metal based ionic liquid crystals are known for various  
 20 transition metals. The majority of the metal-containing ionic  
 21 liquids have the  $[MX_4]^{2-}$  structural building block with  $M =$   
 22 Co, Ni, Cu, Zn, Pd, Cd and  $X = Cl, Br$  and sometimes I.  
 23 Typical counter cations are long-chain quaternary ammonium  
 24 cations,<sup>12,13,14,15</sup> *N*-alkylpyrrolidinium,<sup>16</sup> *N*-alkylpyridinium  
 25 cations,<sup>17,18,19,20,21,22</sup> and 1-alkyl-3-methylimidazolium  
 26 cations<sup>23</sup> Lanthanide based ILCs such as  $[C_{12}mpyr]_3[TbBr_3]$   
 27 ( $C_{12}mpyr = N$ -dodecyl-*N*-methylimidazolium),<sup>24</sup>  
 28  $[C_{12}mim]_3LnBr_6$  ( $C_{12}mim = 1$ -dodecyl-3-methylimidazolium;  
 29  $Ln = Dy, Tb$ )<sup>25</sup> or  $[C_{12}mim]_4[EuBr_6]Br$ .<sup>26</sup>

30 Special interest in the field of such metal-containing  
 31 liquid crystals focuses on light emitting liquid crystals for  
 32 potential applications in emissive LC displays.<sup>27</sup> By  
 33 incorporating 4f-element cations such as  $Eu^{2+}$  or  $Tm^{3+}$   
 34 for blue,  $Eu^{3+}$  or  $Sm^{3+}$  for red and  $Tb^{3+}$  for green emission LCs  
 35 emitting in the three basic colors can be obtained.<sup>28</sup> In  
 36 addition, aligned luminescent LCs can emit polarized light.<sup>29</sup>  
 37 A high magnetic anisotropy of the lanthanide ion as found for  
 38  $Tb^{3+}$ ,  $Dy^{3+}$  and  $Tm^{3+}$  makes the alignment of the mesophase  
 39 in an external magnetic field possible.<sup>30</sup> Thus, such  
 40 compounds might be of interest for the use of electric and  
 41 magnetic switchable devices.<sup>31</sup> However, aside from  
 42 lanthanide-based ILCs another viable way to ionic liquid  
 43 crystalline material which shows lanthanide emission is to  
 44 dope ILCs with suitable lanthanide salts.


45 Here we report on  $C_{12}mimBr$ , a well known ionic liquid  
 46 crystal<sup>32</sup>, doped with  $EuBr_2$ ,  $SmBr_3$ ,  $TbBr_3$  and  $DyBr_3$ , which  
 47 allows to obtain ILC materials which show luminescence in  
 48 the three basic colors. The luminescence properties of the  
 49 obtained hybrid materials are investigated by luminescence  
 50 spectroscopy. The thermal behaviour and mesophase  
 51 formation is investigated by combined thermal (differential  
 52 scanning calorimetry, DSC) and temperature dependent  
 53 polarized optical microscopy (POM).

## 54 Experimental details.

55 Handling of  $C_{12}mimBr$  and  $EuBr_2$  as well as  $LnBr_3$  ( $Ln = Pr,$   
 56  $Sm, Tb, Dy$ ) containing samples was carried out under strict  
 57 inert conditions (vacuum, argon) using advanced Schlenk and  
 58 glove-box techniques.

**1-Dodecyl-3-methylimidazolium bromide,  $C_{12}mimBr$ .** For  
 $C_{12}mimBr$  0.1 mol methylimidazole (99 %, ABCR  
 GmbH&Co, Karlsruhe, D) is dissolved in 70 ml dry  
 acetonitrile. Then 0.1 mol n-dodecylbromide (99 % Acros  
 organics, Geel, B) is added drop-wise and the reaction  
 mixture is heated under reflux for 18 h. After cooling to room  
 temperature most of the solvent is removed under vacuum.  
 Upon adding the concentrated acetonitrile solution to 300 ml  
 cold ( $-30^\circ C$ ) and dry toluene, 1-dodecyl-3-  
 methylimidazolium bromide precipitates as a white powder.  
 The reaction product is filtered off and re-crystallized two  
 times from dry acetonitrile/toluene. The product is dried from  
 any remaining solvent for 48 h under dynamic vacuum.  
 Yield: ~70 %.

$\delta_H$  (298 K, 300 MHz,  $DMSO-d_6$ ): 0.868 [t, 3H, H-1]; 1.234  
 [br. S., 18H, H-2]; 1.766 [quint., 2H, H-3]; 3.848 [s, 3H, H-  
 5]; 4.149 [t, 2H, H-4]; 7.708 [m, 1H, H-6]; 7.777 [m, 1H, H-  
 7]; 9.151 [br. S., 1H, H-8].

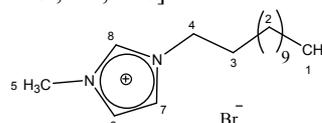

**Scheme 1.** Atom assignment in  $[C_{12}mim]Br$  (1).

MIR (KBr pellet):  $/[cm^{-1}] = 3226.5$  (w), 3149.4 (m),  
 3083.8 (s), 3062.6 (s), 2950.7 (s), 2916.0 (s), 2869.7 (s),  
 2852.4 (s), 1772.4 (w), 1668.2 (w), 1629.7 (m), 1571.8 (m),  
 1473.4 (m), 1427.2 (w), 1384.7 (w), 1344.2 (w), 1317.2 (w),  
 1292.2 (w), 1178.4 (s), 1126.3 (w), 1089.7 (w), 1054.9 (w),  
 1043.4 (w), 1022.2 (w), 1004.8 (w), 943.1 (w), 887.2 (w,  
 shoulder), 862.1 (m), 792.6 (m), 763.7 (w), 742.5 (w), 729.0  
 (w), 715.5 (m), 661.5 (m), 622.9 (m).

FIR (PE pellet):  $/[cm^{-1}] = 562.2$  (m, shoulder), 509.1 (w),  
 498.9 (w), 472.5 (w), 453.2 (m), 417.5 (m), 396.3 (m), 349.1  
 (w), 284.5 (w), 230.5 (w), 154.3 (m, shoulder), 93.5 (s), 64.6  
 (s, shoulder).

Raman:  $/[cm^{-1}] = 3134.2$  (w), 3082.9 (w), 2956.7 (w),  
 2933.6 (s), 2883.5 (s), 2848.7 (s), 2727.2 (w), 1560.4 (vw),  
 1452.4 (w, shoulder), 1432.1 (w), 1421.6 (w, shoulder),  
 1375.3 (vw), 1334.8 (vw), 1296.2 (w), 1128.4 (w), 1105.3  
 (vw), 1087.9 (vw), 1062.9 (w), 1014.6 (w), 887.4 (vw), 733.1  
 (vw), 692.6 (vw), 654.0 (vw), 605.8 (vw), 414.9 (vw), 303.0  
 (vw), 231.6 (vw), 181.5 (vw, shoulder), 150.6 (w, shoulder),  
 114.0 (w), 85.1 (w, shoulder).

Elemental analysis (%) calcd for  $[C_{12}mim]Br$ : C 58.00, H  
 9.43, N 8.45; found: C 57.63, H 9.74, N 8.42.

**$EuBr_2$ .** According to a literature procedure<sup>33</sup> 2.8 g (8 mmol)  
 europium(III) oxide (99.97%, Fluka Chemie, Buchs, CH) are  
 dissolved in 80 ml conc. HBr (48%, Aldrich, Steinheim, D)  
 and 11 g (0.112 mol) ammonium bromide (99.995%, Merck,  
 Darmstadt, D) are added. After all starting materials are  
 dissolved the solvent is boiled off. The residual yellow solid  
 is heated under vacuum at  $120^\circ C$  ( $20^\circ C/h$ ) for 6 h, then at  
 $400^\circ C$  ( $20^\circ C/h$ ) for 12 h before cooling to room temperature  
 ( $20^\circ C/h$ ). The obtained  $EuBr_2$  is checked for identity and  
 purity by PXRD (powder X-ray diffraction).

**LnBr<sub>3</sub> (Ln = Sm, Tb, Dy).** LnBr<sub>3</sub> was synthesised according to a modified literature procedure.<sup>34</sup> For SmBr<sub>3</sub> and DyBr<sub>3</sub> 0.005 mol of the respective lanthanide(III) oxide (99.9% Fluka Chemie AG, Buchs, CH) and 0.07 mol ammonium bromide (suprapur® 99.995% Merck, Darmstadt, D), for TbBr<sub>3</sub> 0.004 mol Tb<sub>4</sub>O<sub>7</sub> (99.9% Fluka Chemie AG, Buchs, CH) and 0.102 mol ammonium bromide were dissolved in 48% conc. aqueous hydrobromic acid (Aldrich, Steinheim, D). After removing the solvent, the formed (NH<sub>4</sub>)<sub>3</sub>LnBr<sub>6</sub>·yH<sub>2</sub>O is decomposed to LnBr<sub>3</sub> at elevated temperatures where also any excess of ammonium bromide sublimes off. The crude LnBr<sub>3</sub> is then purified by sublimation under vacuum (< 10<sup>-5</sup> mbar). The purity of the obtained LnBr<sub>3</sub> is checked by PXRD.

**LnX<sub>2</sub>/LnX<sub>3</sub> in C<sub>12</sub>mimBr.** To obtain lanthanide halide containing C<sub>12</sub>mimBr samples the respective amounts of the lanthanide bromide and 1-dodecyl-3-methylimidazolium bromide are heated in a sealed silica ampoule under vacuum at 120°C until a homogeneous mixture is obtained. After cooling to room temperature waxy solids are obtained which are subjected to further analysis. Alternatively the lanthanide halide and C<sub>12</sub>mimBr can be dissolved in CH<sub>2</sub>Cl<sub>2</sub> at room temperature. After removal of the solvent under vacuum, again, waxy samples of the desired composition are obtained.

**Instrumentation.** Elemental analyses were obtained on an Euro Vektor elemental analyzer EuroEA 3000 (HEKAtech GmbH, Wegberg, D) for C<sub>12</sub>mimBr.

<sup>1</sup>H-Nuclear magnetic resonance (NMR) spectra were recorded on a Bruker AC-300 spectrometer (operating at 300 MHz for <sup>1</sup>H) (Bruker Germany GmbH, D).

IR spectra of the solid were recorded using a IFS-66V-S Fourier Transform IR spectrometer (Bruker Optik GmbH, Ettlingen, D); samples were measured pressed in a polyethylene matrix for far IR range (50-600 cm<sup>-1</sup>) and in a KBr matrix for middle IR (MIR) range (600-4000 cm<sup>-1</sup>).

Raman spectra were recorded with a FRA 106-S Fourier Transform Raman spectrometer (Bruker Optik GmbH, Ettlingen, D) at 150mW. Raman samples were measured in glass capillaries with an inner diameter of 0.1 cm and 0.15 mm wall thickness.

Differential scanning calorimetry (DSC) was performed with a computer-controlled Phoenix DSC 204 F1 thermal analyser (Netzsch, Selb, D) with argon as protection gas. The samples were placed in aluminium pans which were cold-sealed under argon. Experimental data are displayed in such a way that exothermic peaks occur at negative heat flow and endothermic peaks at positive heat flow. Heating and cooling rates were 5°C/min. Given temperatures correspond to the onset of the respective thermal process.

Optical polarizing microscopy was carried out with an Axio Imager A1 microscope (Carl Zeiss MicroImaging GmbH, Göttingen, D) equipped with a hot stage THMS600 (Linkam Scientific Instruments Ltd, Surrey, UK) and a temperature controller Linkam TMS 94 (Linkam Scientific Instruments Ltd, Surrey, UK) and crossed polarizers. Images were recorded at a magnification of 100× as movies with a digital camera after initial heating during the cooling stage. Heating and cooling rates were 5 K/min<sup>-1</sup>. For the measurement the samples were placed under argon between

two cover slips which were sealed with a two-component adhesive (UHU plus 300, UHU GmbH & Co. KG, Bühl, D).


UV-Vis spectra were obtained with a Cary 5000 spectrometer (Bruker, Bremen, Germany) at room temperature. Excitation and emission spectra and also luminescence decays were recorded on a Jobin Yvon Horiba Fluorolog FL3-22 (HORIBA Jobin Yvon Inc., Unterhaching, D) with a xenon lamp as the excitation source and a photomultiplier tube for detection. Interconfigurational f-f-transitions are assigned according to the Dieke diagram.<sup>35</sup>

## Results and Discussion

### C<sub>12</sub>mimBr


Dry C<sub>12</sub>mimBr was chosen as a host matrix with liquid crystalline properties and doped with various amounts of EuBr<sub>2</sub>, SmBr<sub>3</sub>, TbBr<sub>3</sub> and DyBr<sub>3</sub>.

DSC measurements show that upon cooling liquid samples of C<sub>12</sub>mimBr from the isotropic melt a liquid to liquid crystalline (L↔LC) phase transition occurs at 99.2°C and a liquid crystalline to crystalline phase transition at 14.2°C (LC↔S). Upon heating the samples undergo two solid-solid (S↔SI) phase transitions at 2.0 and 7.2°C which probably belong to order-disorder transitions of the imidazolium alkyl chains. Then the reversible crystalline solid ↔ liquid crystalline (S↔LC) and liquid crystalline ↔ isotropic liquid (LC↔L) transitions are observed at 42.0°C and 100.2°C, respectively (Fig. 1).

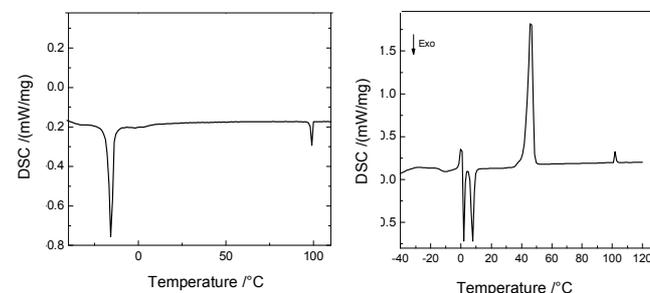


**Figure 1.** DSC thermograms of neat [C<sub>12</sub>mim]Br. 1<sup>st</sup> cooling (left) and 2<sup>nd</sup> heating (right).

The enantiotropic liquid crystalline mesophase can be identified as a smectic A phase by polarizing optical microscopy (POM). The POM micrographs show focal conic fan textures with dark homeotropic areas. The dark homeotropic areas where no birefringence is observed when the long axis of the imidazolium cations is aligned parallel to the incident polarized light so that the light wavevector can not be rotated. The focal conic fan textures originate when a layered structure forms conical domains.

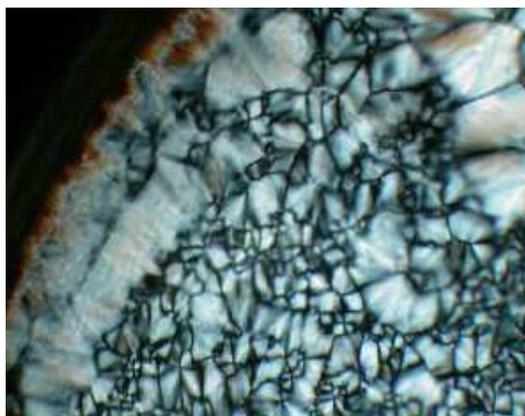

**Figure 2.** POM micrographs of the LC state of  $C_{12}mimBr$ .

$C_{12}mimBr$  alone shows a bluish photoluminescence which is due to electronic transitions within the imidazolium head group. It is well known that the imidazolium  $\pi$  electron system can be excited with UV radiation.<sup>36</sup> The energy of the excited state cannot be easily converted into vibrational energy as mixing between  $\pi$  and  $\sigma$  orbitals of imidazolium is negligible and, in consequence, photoluminescence can be observed. The photoluminescence of  $C_{12}mimBr$  at  $\lambda(em) = 450$  nm after excitation with  $\lambda(ex) = 366$  nm is due to the allowed ( $^1\pi \leftarrow ^1\pi^*$ ) transition (Fig. 3). The fluorescence decay time is too short to be measured (ns regime). Phosphorescence measurements reveal a second, weaker emission which is detected at  $\lambda(em) = 515$  nm for the  $C_{12}mim$  that can be assigned to the spin forbidden ( $^1\pi \leftarrow ^3\pi^*$ ) transition (Fig. 3). Measurements of the luminescence intensity decay reveals a lifetime of  $\sim 200$   $\mu s$  for the ( $^1\pi \leftarrow ^3\pi^*$ ) transition.

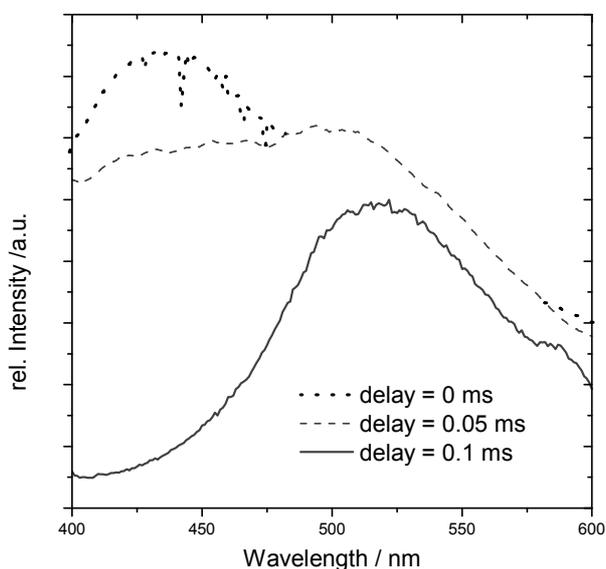


**Figure 3.** Photoluminescence of  $C_{12}mimBr$  at 77K,  $\lambda(ex) = 366$  nm.


#### *EuBr<sub>2</sub> in C<sub>12</sub>mimBr*

Figure 4 shows the thermal behaviour of  $C_{12}mimBr$  doped with different amounts of europium dibromide. All samples show the formation of a liquid crystalline state of matter. By

POM measurements the mesophase can be identified as a smectic A phase (Fig. 5) similar to the mesophase formed by neat  $C_{12}mimBr$ . Samples with 0.5 and 1.0 mol%  $EuBr_2$  show only small deviations with respect to their thermobehaviour when compared that of neat  $C_{12}mimBr$ . The  $S \leftrightarrow LC$  transitions are found at 37.6°C (0.5 mol%  $EuBr_2$ ) and 27.5°C (1.0 mol%  $EuBr_2$ ) compared to 38.8°C for neat  $C_{12}mimBr$ . The  $LC \leftrightarrow L$  transitions are detected at 98.8°C (0.5 mol%  $EuBr_2$ ) and 101.4°C (1.0 mol%  $EuBr_2$ ) compared to 98.6°C for neat  $C_{12}mimBr$ . Larger concentrations of  $EuBr_2$  favour the LC state. In samples containing 1.9 and more mol%  $EuBr_2$  the mesophasic region is extended drastically and the liquid crystalline state is even stable at room temperature and below. The  $LC \leftrightarrow L$  transitions occur at 0.7°C (0.9 mol%  $EuBr_2$ ), 0.5°C (2.2 mol%  $EuBr_2$ ) and 0.3°C (1.0 mol%  $EuBr_2$ ). The clearing points are detected at temperatures similar to that for neat  $C_{12}mimBr$  (100 °C for 0.9 mol%  $EuBr_2$ , 99.5°C for 2.2 mol%  $EuBr_2$  and 100.3°C for 2.9 mol%  $EuBr_2$ ).

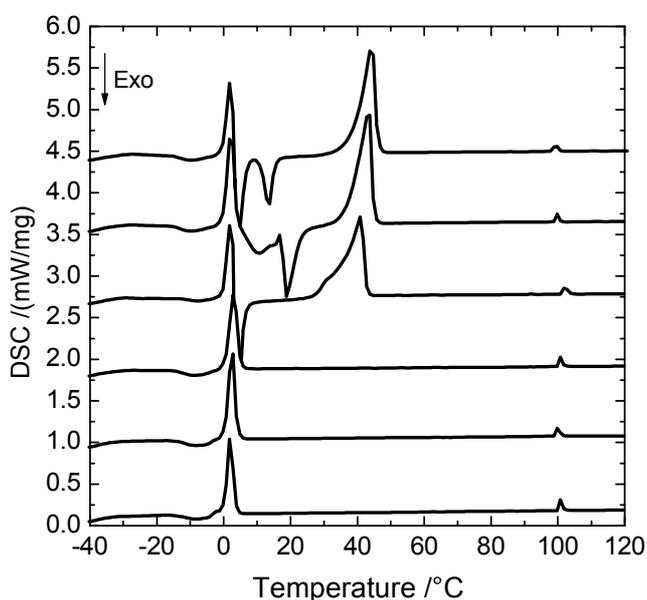


**Figure 4.** DSC thermograms of  $C_{12}mimBr$  (top) and  $C_{12}mimBr$  doped with different 0.5, 1.0, 1.9, 2.2 and 2.9 mol%  $EuBr_2$  (from top to bottom, 2<sup>nd</sup> heating cycle).

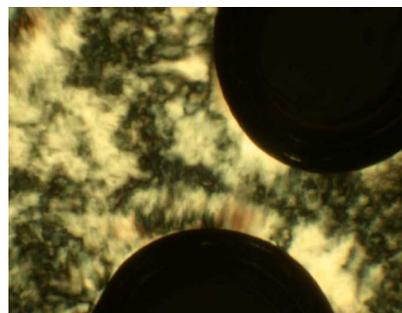

**Figure 5.** Typical POM micrographs of a  $EuBr_2$ -doped  $C_{12}mimBr$  sample in the LC state.

All  $EuBr_2$  containing samples show an intense yellow color in agreement with the UV-Vis spectrum where an absorption around 420 nm can be detected (Fig. 6, left). This absorption

is due to the  $f \rightarrow d$ -transition of  $\text{Eu}^{2+}$  and lies in the expected region.

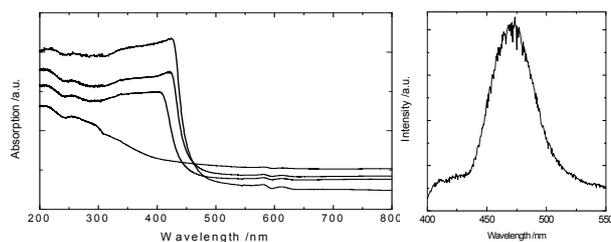


**Figure 6.** Left: UV-Vis absorption spectrum of  $\text{C}_{12}\text{mimBr}$  (bottom) and  $\text{C}_{12}\text{mimBr}$  doped with 0.5, 1.9 and 2.9 mol%  $\text{EuBr}_2$ . Right: Photoluminescence spectrum of  $\text{C}_{12}\text{mimBr}$  with 2.9 mol%  $\text{EuBr}_2$  ( $T = 77\text{K}$ ,  $\lambda(\text{ex}) = 350\text{nm}$ ).

At low temperatures (77 K) a weak blue emission of  $\text{Eu}^{2+}$  can be detected (Fig. 6, right). The emission band shows the typical quite symmetric bell shape expected for  $\text{Eu}^{2+}$ . The emission maximum upon excitation with  $\lambda(\text{ex}) = 350\text{nm}$  is observed at 473 nm. This value lies between that found for  $\text{KMgBr}_3:\text{Eu}^{2+}$  (470 nm)<sup>37</sup> and  $\text{CsCdBr}_3:\text{Eu}^{2+}$  (476 nm)<sup>38</sup>.


#### *SmBr<sub>3</sub> in C<sub>12</sub>mimBr*

Similar to the investigations for  $\text{EuBr}_2$  1.1 mol%  $\text{SmBr}_3$  was doped into  $\text{C}_{12}\text{mimBr}$ . The thermal behaviour of this sample is similar to that of  $\text{C}_{12}\text{mimBr}$  with 1.0 mol%  $\text{EuBr}_2$  (Fig. 7). In this case, the smectic mesophase could be stabilized from about  $-9^\circ\text{C}$  up to  $105^\circ\text{C}$ .

Low temperature photophysical investigations show aside from transitions in the  $\pi$ -system of imidazolium the characteristic  $f$ - $f$  transitions of  $\text{Sm}^{3+}$  at 567 nm ( $^4\text{G}_{5/2} \rightarrow ^6\text{H}_{5/2}$ ), 601 nm ( $^4\text{G}_{5/2} \rightarrow ^6\text{H}_{7/2}$ ), 648 nm ( $^4\text{G}_{5/2} \rightarrow ^6\text{H}_{9/2}$ ) and 710 nm ( $^4\text{G}_{5/2} \rightarrow ^6\text{H}_{11/2}$ ) (Fig. 8).

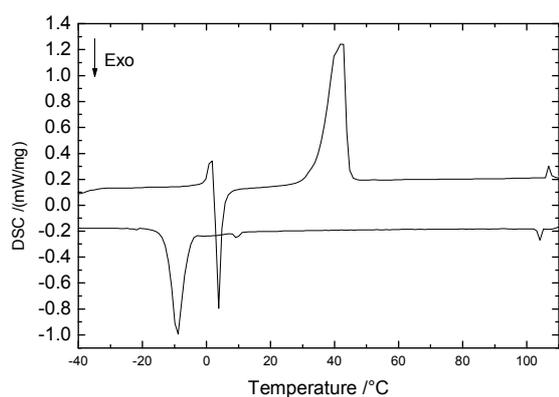


**Figure 7.** DSC thermogram of  $\text{C}_{12}\text{mimBr}$  with 1.1 mol%  $\text{SmBr}_3$  (1<sup>st</sup> cooling (top) and 2<sup>nd</sup> heating cycle (bottom)).

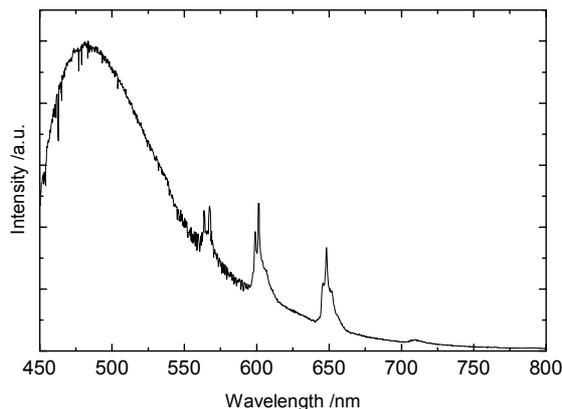


**Figure 8.** Emission spectrum of  $\text{C}_{12}\text{mimBr}$  with 1.1 mol%  $\text{SmBr}_3$  ( $\lambda_{\text{ex}} = 310\text{nm}$ , 77k).

#### *TbBr<sub>3</sub> in C<sub>12</sub>mimBr*

Doping  $\text{C}_{12}\text{mimBr}$  with 1.1 mol%  $\text{TbBr}_3$  yielded a liquid crystalline phase which showed a thermal behavior similar to  $\text{C}_{12}\text{mimBr}:\text{Sm}^{3+}$ . Upon cooling liquid crystalline mesophase formation is observed from about  $100^\circ\text{C}$  down to about  $-10^\circ\text{C}$  (Fig. 9). Polarizing optical microscopy suggests that a smectic A phase is formed (Fig. 10).

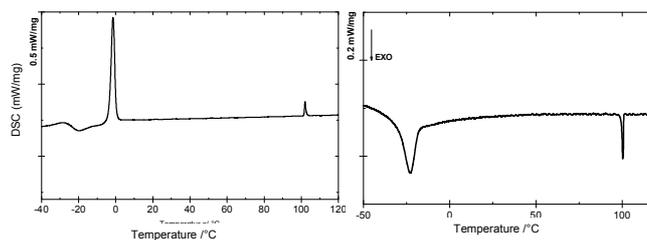


**Figure 9.** DSC thermogram of  $\text{C}_{12}\text{mimBr}$  with 1.0 mol%  $\text{TbBr}_3$  (1<sup>st</sup> cooling (left) and 2<sup>nd</sup> heating cycle (right)).

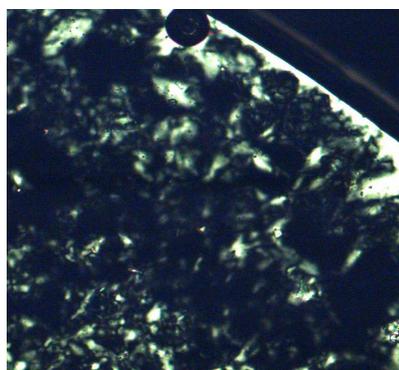

**Figure 10.** Typical POM micrographs of a  $\text{TbBr}_3$ -doped  $\text{C}_{12}\text{mimBr}$  sample in the LC state.

Strong greenish luminescence is observed (Fig. 11). The transitions occur at 488, 494 nm ( $^5\text{D}_4 \rightarrow ^7\text{F}_6$ ), 543, 548 nm

( $^4D_4 \rightarrow ^7F_5$ ), 583, 590 nm ( $^4D_4 \rightarrow ^7F_4$ ), 620 nm ( $^4D_4 \rightarrow ^7F_3$ ) and 650 nm ( $^4D_4 \rightarrow ^7F_2$ ).

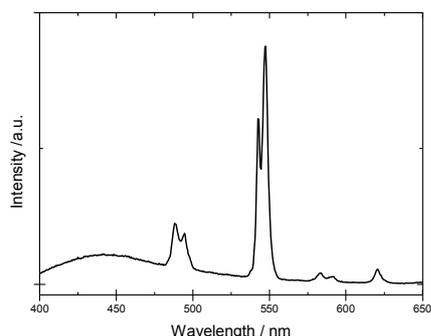


**Figure 11.** Emission spectrum of  $C_{12}mimBr$  with 1.1 mol%  $TbBr_3$  ( $\lambda_{ex} = 310$  nm, 77k).


Most interestingly the emission color of the system can be tuned by the choice of the respective excitation wavelength. While excitation with  $\lambda_{ex} = 377$  nm leads to the typical yellowish-green emission of  $Tb^{3+}$ , excitation with  $\lambda_{ex} = 400$  nm yields the typical white emission of  $C_{12}mimBr$  (Fig. 12, top and middle). The lifetime of the most intense f-f  $Tb^{3+}$  transition is with  $\tau = 3.4$  ms astonishingly high.

*DyBr<sub>3</sub> in C<sub>12</sub>mimBr*


The system  $C_{12}mimBr:Dy^{3+}$  (9:1) behaves both thermally as well as photophysically similar to the analogous  $C_{12}mimBr:Tb^{3+}$  system. Again, mesophase formation is observed in the range from 100°C down to  $\sim -10^\circ C$  (Fig. 12). The textures observed by optical polarizing microscopy point to a smectic mesophase (Fig. 14).

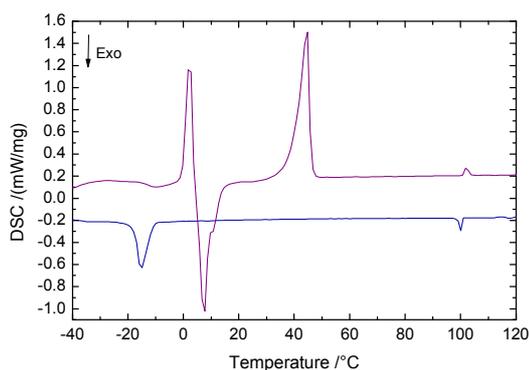

**Figure 13.** DSC thermogram of  $C_{12}mimBr: Dy^{3+}$ .

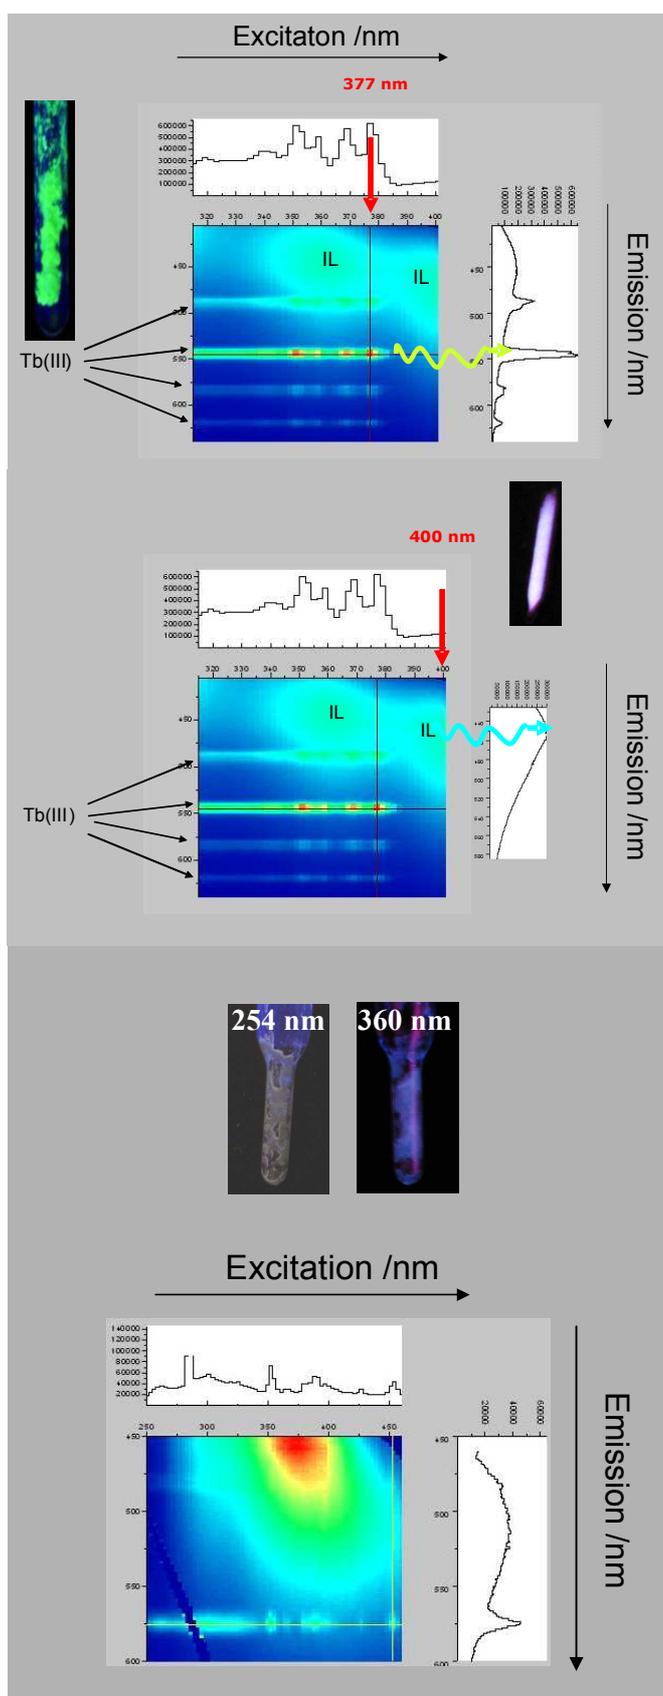


**Figure 12.** Top and middle: 2D excitation-emission spectra of  $C_{12}mimBr:Tb^{3+}$ ; bottom: 2D excitation-emission spectra of  $C_{12}mimBr: Dy^{3+}$ . The photos show the sample under irradiation with short and longer wavelength UV light.

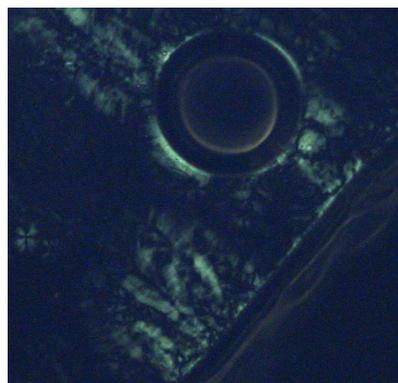

**Figure 14.** Typical POM micrographs of a DyBr<sub>3</sub>-doped C<sub>12</sub>mimBr sample in the LC state.

C<sub>12</sub>mimBr doped with DyBr<sub>3</sub> shows strong luminescence with transitions at 578 nm (<sup>4</sup>F<sub>9/2</sub>→<sup>6</sup>H<sub>13/2</sub>), 668 nm (<sup>4</sup>F<sub>9/2</sub>→<sup>6</sup>H<sub>11/2</sub>) and 754 nm (<sup>4</sup>F<sub>9/2</sub>→<sup>6</sup>F<sub>11/2</sub>, <sup>6</sup>H<sub>9/2</sub>) (Fig. 15).

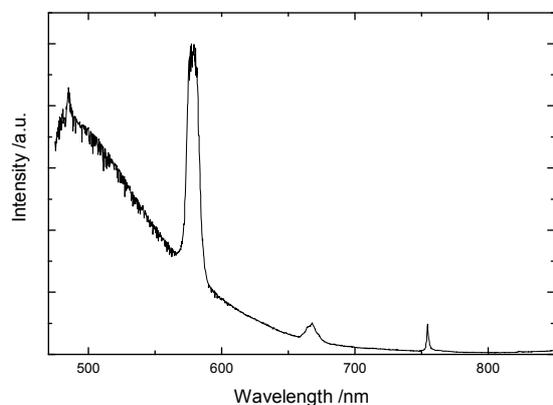

**Figure 15.** Emission spectrum of C<sub>12</sub>mimBr with 1.1 mol% DyBr<sub>3</sub> ( $\lambda_{\text{ex}} = 310 \text{ nm}$ , 77k).


As for TbBr<sub>3</sub> in C<sub>12</sub>mimBr the emission color can be tuned by the choice of the respective excitation wavelength. While excitation with the short wavelength  $\lambda_{\text{ex}} = 254 \text{ nm}$  leads to the characteristic yellowish emission of Dy<sup>3+</sup>, excitation with  $\lambda_{\text{ex}} = 360 \text{ nm}$  results in a bluish white emission which originates from the superposition of Dy<sup>3+</sup> and C<sub>12</sub>mimBr emissions (Fig. 12, bottom). The lifetime of the most intense f-f Dy<sup>3+</sup> transition is determined to  $\tau = 53 \mu\text{s}$ .

## Conclusions

Ln<sup>2+</sup> and Ln<sup>3+</sup> doped C<sub>12</sub>mimBr turn out to be promising new soft optical materials. The host material C<sub>12</sub>mimBr itself is an ionic liquid crystal. Lanthanide bromide dopant concentrations of up to ~1 mol% seem to have only little effect on the liquid crystalline properties of the host material. All doped materials form layered liquid crystalline mesophases even at room temperature. At the same time all compounds show reasonably good luminescence. Whilst neat C<sub>12</sub>mimBr shows a bluish white emission, by doping

C<sub>12</sub>mimBr with EuBr<sub>2</sub> blue luminescence can be achieved. Analogous Eu<sup>3+</sup> or Sm<sup>3+</sup> materials show a strong red luminescence.

Of special interest is the observation, that the emission color of C<sub>12</sub>mimBr doped with TbBr<sub>3</sub> and DyBr<sub>3</sub> allows for the tuning of the emission color by a mere change of the excitation light wavelength. In case of TbBr<sub>3</sub> the color can be changed between green (mainly Tb<sup>3+</sup>) emission and white whereas in case of DyBr<sub>3</sub> a switch between orange-yellow and bluish white is possible. It turns out that doping C<sub>12</sub>mimBr with various lanthanide bromides yields interesting new materials which show strong luminescence in the basic colors (Fig. 16) and might be used in active displays in the future.

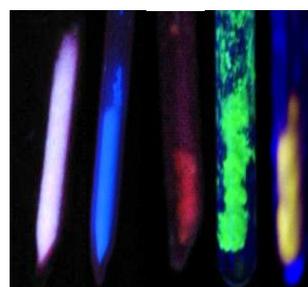

**Figure 16.** Neat C<sub>12</sub>mimBr (left) doped with various lanthanide bromides under UV-light.

**Acknowledgements.** This work was supported by the State of Nordrhein-Westfalen, the Universität zu Köln, the Ruhr-Universität Bochum as well as by the Deutsche Forschungsgemeinschaft, Bonn.

## References

- <sup>1</sup> A. Mele, G. Romano, M. Giannone, E. Ragg, G. Fronza, G. Raos, V. Marcon, *Angew. Chem. Int. Ed.* **2006**, *45*, 1123.
- <sup>2</sup> P.J. Collings, M. Hird, *Introduction to Liquid Crystals: Chemistry and Physics*, Taylor & Francis, 1997.
- <sup>3</sup> V.G. Chigrinov, *Liquid Crystal Devices*, Artech House Optoelectronic Library, 1999.
- <sup>4</sup> C. M. Gordon, J. D. Holbrey, A. R. Kennedy, K. R. Seddon, *J. Mater. Chem.* **1998**, *8*, 2627.
- <sup>5</sup> E. Alami, H. Levy, R. Zana, P. Weber, A. Skoulios, *Liq. Cryst.* **1993**, *13*, 201.
- <sup>6</sup> X. Wang, F.W. Heinemann, M. Yang, B. Melcher, M. Fekete, A.-V. Mudring, P. Wasserscheid, K. Meyer, *Chem. Commun.* **2009**, DOI: 10.1039/b914939b.
- <sup>7</sup> S. Ujiie, K. Imura, *Macromolecules*, **1992**, *25*, 3174.
- <sup>8</sup> For an overview see: K. Binnemans *Chem. Rev.* **2005**, *105*, 4148.
- <sup>9</sup> J.L. Serrano, (Ed.), *Metallomesogens, Synthesis, Properties and Applications*, Wiley-VCH, Weinheim, 1996; F. Neve, F. Adv. Mater. **1996**, *8*, 277; B. Donnio, D.W. Bruce, 'Metallomesogens' in *Liquid Crystals II*, edit. by D.M.P.

- Mingos, Springer, Berlin, **1999**, 193; R. Giménez, D.P. Lydon, J.L. Serrano, *Current Opinion in Solid State and Materials Science*, 2002, **6**, 527; I.J.B. Lin, C.S. Vasam, *J. Organomet. Chem.* 2005, **690**, 3498.
- <sup>10</sup> F. Neve, *Adv. Mat.* **1996**, *8*, 277; I. J. B. Lin, C.S. Vasam, C. S. J. *Organomet. Chem.* 2005, **690**, 3498; N. Hoshino, *Coord. Chem. Rev.* **1998**, *174*, 77; P.J. Alonso, *Metallomesogens* **1996**, 387; P.J. Alonso, *Metallomesogens* **1996**, 349; P. Espinet, M.A. Esteruelas, L. A. Oro, J.L. Serrano, E. Sola, *Coord. Chem. Rev.* 1992, **117**, 215.
- <sup>11</sup> K. Binnemans, C. Görrler-Walrand, C. *Chem. Rev.* **2002**, *102*, 2303; C. Piguet, J.C.G. Bünzli, B. Donnio, D. Guillon, D. *Chem. Commun.* **2006**, 3755; E. Terazzi, S. Suarez, S. Torelli, H. Nozary, D. Imbert, O. Mamula, J.-P. Rivera, E. Guillet, J.M. Bénech, G. Bernardinelli, R. Scopelliti, B. Donnio, D. Guillon, J.-C.G. Bünzli, C. Piguet, C. *Adv. Funct. Mater.* **2006**, *16*, 157.
- <sup>12</sup> V. Salerno, A. Grieco, M. Vacatello, *J. Phys. Chem.* **1976**, *80*, 2444.
- <sup>13</sup> G.F. Needham, R.D. Willett, H.F. Franzen, H. F. *J. Chem. Phys.* **1984**, *88*, 674.
- <sup>14</sup> E. Landi, M. Vacatello, M. *Thermochimica Acta* **1975**, *13*, 441.
- <sup>15</sup> A. Kanazawa, T. Ikeda, Y. Nagase, Y. *Chem. Mater.* **2000**, *12*, 3776.
- <sup>16</sup> K. Goossens, K. Lava, P. Nockemann, K. Van Hecke, L. Van Meervelt, P. Pattison, K. Binnemans, Th. Cardinaels, *Langmuir* **2009**, *25*, 5881; A. Getsis, A.-V. Mudring, Z. *Anorg. Allg. Chem.* **2009**, 635, 2214.
- <sup>17</sup> C.J. Bowlas, D.W. Bruce, K.R. Seddon, *Chem. Commun.* **1996**, 1625.
- <sup>18</sup> F. Neve, A. Crispini, S. Armentano, O. Francescangeli, *Chem. Mater.* **1998**, *10*, 1904.
- <sup>19</sup> F. Neve, O. Francescangeli, A. Crispini, J. Charmant, J. *Chem. Mater.* **2001**, *13*, 2032.
- <sup>20</sup> F. Neve, O. Francescangeli, A. Crispini, A. *Inorg. Chim. Acta* **2002**, 338, 51.
- <sup>21</sup> F. Neve, M. Impéror-Clerc, *Liq. Cryst.* **2004**, *31*, 907.
- <sup>22</sup> A. Taubert, *Angew. Chem. Int. Ed.* **2004**, *43*, 5380.
- <sup>23</sup> C.K. Lee, H.H. Peng, I.J.B. Lin, I. J. B. *Chem. Mater.* **2004**, *16*, 530.
- <sup>24</sup> A. Getsis, *Dissertation*, Universität zu Köln, 2009.
- <sup>25</sup> A. Getsis, B. Balke, C. Felser, A.-V. Mudring, *Cryst. Growth & Des.* **2009**, *9*, 4427.
- <sup>26</sup> A. Getsis, S. Tang, A.-V. Mudring, *Eur. J. Inorg. Chem.* 2010, in press.
- <sup>27</sup> M. Grell, D.C. Bradley, *Adv. Mat.* 1999, **11**, 895; M. O'Neill, S.M. Kelley, *Adv. Mat.* 2003, **15**, 1135.
- <sup>28</sup> L.N. Puntus, K.J. Schenk, J.C.G. Bünzli, *Eur. J. Inorg. Chem.* 2005, **23**, 4739; J. Kocher, F. Gumy, A.-S. Chauvin, J.C.G. Bünzli, *J. Mat. Chem.* **2007**, *17*, 654.
- <sup>29</sup> Y. G. Galyametdinov, A.A. Knyazev, V.I. Dzhabarov, T. Cardinaels, K. Driesen, C. Görrler-Walrand, K. Binnemans, K. *Adv. Mat.* **2008**, *20*, 252; Y.G. Galyametdinov, W. Haase, B. Goderis, D. Moors, K. Driesen, R. Van Deun, K. Binnemans, *J. Phys. Chem. B* **2007**, *111*, 13881.
- <sup>30</sup> Y. Galyametdinov, M.A. Athanassopoulou, K. Griesar, O. Kharitonova, E.A. Soto Busmante, L. Tinchurina, I. Ovchinnikov, I.; Haase, W. *Chem. Mat.* **1996**, *8*, 922; K. Binnemans, Y.G. Galyametdinov, R. Van Deun, D.W. Bruce, S.R. Collinson, A.P. Polishchuk, I. Bikchantaev, W. Haase, A.V. Prosvirin, L. Tinchurina, I. Litvinov, A. Gubajdullin, A. Rakhmatullin, K. Uytterhoeven, L. Van Meervelt, *J. Am. Chem. Soc.* **2000**, *122*, 4335; V.S. Mironov, Y.G. Galyametdinov, A. Ceulemans, K. Binnemans, K. *J. Chem. Phys.* **2000**, *113*, 10293; Y.G. Galyametdinov, W. Haase, L. Malykhina, A. Prosvirin, I. Bikchantaev, A. Rakhmatullin, K. Binnemans, *Chem. Eur. J.* **2001**, *7*, 99; Y. Galyametdinov, G. Ivanova, I. Ovchinnikov, A. Prosvirin, D. Guillon, B. Heinrich, D.A. Dunmur, D.W. Bruce, *Liq. Cryst.* **1996**, *20*, 831; K. Binnemans, L. Malykhina, V.S. Mironov, W. Haase, K. Driesen, R. Van Deun, L. Fluyt, C. Görrler-Walrand, Y.G. Galyametdinov, Y.G. *ChemPhysChem.* **2001**, *p 2*, 680.
- <sup>31</sup> C. Piguet, J.C.G. Bünzli, B. Donnio, D. Guillon, D. *Chem. Commun.* **2006**, 3755.
- <sup>32</sup> A. Getsis, A.-V. Mudring, *Cryst. Res. Technol.* **2008**, *43*, 1187.
- <sup>33</sup> G. Meyer, S. Dötsch, T. Staffel, *J. Less – Common Met.* **1987**, *127*, 155.
- <sup>34</sup> G. Meyer, S. Dötsch, T. Staffel, *J. Less – Common Met.* **1987**, *127*, 155.
- <sup>35</sup> G.H. Dieke, *Spectra and energy levels of rare earth ions in crystals*, Interscience Publishers, New York, **1968**; W.T. Carnall, H.M. Crosswhite, H. Crosswhite, *Energy level structure and transition probabilities in the spectra of trivalent lanthanides in LaF<sub>3</sub>*, Special Report **1977** (Argonne, IL: Chemistry Division, Argonne National Laboratory).
- <sup>36</sup> M.D. Lumb, *Luminescence spectroscopy*, Academic Press, London (1978).
- <sup>37</sup> P. P. Larsen, *Dissertation*, Universität zu Köln, **2004**.
- <sup>38</sup> F. Pelle, N. Gardant, M. Genotelle, Ph. Goldner, P. Pocher, *J. Phys. Chem. Solids* **1995**, *56*, 1003.