



**HAL**  
open science

# Mössbauer-spectroscopic characterization of the local surrounding of tin dopant cations in the bulk and on the surface of YCrO<sub>3</sub> crystallites

Mikhail I. Afanasov, Alain Wattiaux, Christine Labrugère, Pavel B. Fabritchnyi, Claude Delmas

## ► To cite this version:

Mikhail I. Afanasov, Alain Wattiaux, Christine Labrugère, Pavel B. Fabritchnyi, Claude Delmas. Mössbauer-spectroscopic characterization of the local surrounding of tin dopant cations in the bulk and on the surface of YCrO<sub>3</sub> crystallites. *Zeitschrift für Naturforschung B*, 2011, 66 (3), pp.239-244. 10.1515/znb-2011-0305 . hal-00580072

**HAL Id: hal-00580072**

**<https://hal.science/hal-00580072>**

Submitted on 17 Jun 2022

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution - NonCommercial - NoDerivatives 4.0 International License

# Mössbauer-spectroscopic Characterization of the Local Surrounding of Tin Dopant Cations in the Bulk and on the Surface of $\text{YCrO}_3$ Crystallites

Mikhail I. Afanasov<sup>a</sup>, Alain Wattiaux<sup>b</sup>, Christine Labrugère<sup>b</sup>, Pavel B. Fabritchnyi<sup>a</sup>, and Claude Delmas<sup>b</sup>

<sup>a</sup> Department of Chemistry, M. V. Lomonosov Moscow State University, 119899 Moscow V-234, Russia

<sup>b</sup> CNRS, Université de Bordeaux, Institut de Chimie de la Matière Condensée de Bordeaux, 87, avenue du Dr. A. Schweitzer, 33608 Pessac Cedex, France

Reprint requests to Prof. Pavel B. Fabritchnyi. Fax: (7)495 9393187. E-mail: pf@radio.chem.msu.ru

*Z. Naturforsch.* **2011**, *66b*, 239–244; received January 7, 2011

$^{119}\text{Sn}$  Mössbauer spectra of tin-doped  $\text{YCrO}_3$ , obtained by annealing in air of an  $\text{YCr}(\text{}^{119}\text{Sn}^{4+})_{0.003}(\text{OH})_6 \cdot x\text{H}_2\text{O}$  precursor, provide evidence for the location of  $\text{Sn}^{4+}$  on the  $\text{Cr}^{3+}$  site in the bulk of crystallites. Below the Néel point of  $\text{YCrO}_3$  ( $T_N = 141$  K),  $\text{Sn}^{4+}$  ions are spin-polarized, the majority exhibiting a hyperfine field  $H$  of 80 kOe at 4.2 K. Analysis of the  $^{119}\text{Sn}$  spectra of another sample, obtained by impregnation of polycrystalline  $\text{YCrO}_3$  with a solution of  $^{119}\text{SnCl}_4$ , shows that annealing in  $\text{H}_2$  results in the location of the dopant, in the divalent state, on the surface of the crystallites. The parameters of an *in situ*  $^{119}\text{Sn}$  spectrum at 295 K (isomer shift  $\delta = 2.76$  mm  $\text{s}^{-1}$  and quadrupole splitting  $E_Q = 1.95$  mm  $\text{s}^{-1}$ ) reveal the presence of  $\text{Sn}^{2+}$  ions on sites with a coordination number  $\text{CN} < 6$ . At 100 K these  $\text{Sn}^{2+}$  ions exhibit no spin polarization. Upon contact with air they are rapidly oxidized to the tetravalent state, as demonstrated by their modified isomer shift value  $\delta = 0.06$  mm  $\text{s}^{-1}$ . For the large majority of both the residual “parent”  $\text{Sn}^{2+}$  ions and the “daughter”  $\text{Sn}^{4+}$  ones no spin polarization is observed down to 4.2 K. This means that surface-located tin dopant cations, regardless of their oxidation state, occupy the  $\text{Y}^{3+}$  sites with an equal number of  $\text{Cr}^{3+}$  neighbors having mutually opposite spin orientations.

**Key words:**  $\text{YCrO}_3$ ,  $^{119}\text{Sn}$  Mössbauer Spectroscopy, Bulk and Surface Sites

## Introduction

The first Mössbauer spectroscopic investigations of the hyperfine interactions of the  $^{119}\text{Sn}^{4+}$  dopant in  $R\text{CrO}_3$  ( $R = \text{La}, \text{Y}, \text{Lu}$ ) antiferromagnetic orthochromites [1, 2] aimed to elucidate the mechanism of spin polarization of the diamagnetic tin cations by their magnetically active  $\text{Cr}^{3+}$  neighbors in perovskite-related structures. Recently, one of these orthochromites,  $\text{LuCrO}_3$ , was investigated in order to determine the location of the  $^{119}\text{Sn}$  probe on surface sites of crystallites [3]. Some  $R\text{CrO}_3$  compounds are actually utilized both as materials for semiconductor gas sensors and as catalysts in certain practically relevant processes, *e. g.* the oxidation of CO or  $\text{C}_3\text{H}_6$  by  $\text{O}_2$  [4]. The location of  $^{119}\text{Sn}$  on the solid-gas interface would allow one to characterize, using the Mössbauer effect, the impact of tin additives on surface-sensitive properties of such materials. These experiments [3] have

demonstrated that it is possible to stabilize the  $^{119}\text{Sn}$  probes on the surface of  $\text{LuCrO}_3$ . However, it remained unclear whether the synthesis procedure developed in this study [3] may also be used to locate tin cations on the surface of other  $R\text{CrO}_3$  substrates. In this paper, we report new results concerning  $^{119}\text{Sn}$  dopant ions in  $\text{YCrO}_3$ . This chromite was chosen for the following reasons: (i) the value of the magnetic field  $H$  at the  $\text{Sn}^{4+}$  cations on the  $\text{Cr}^{3+}$  site in the bulk of crystallites is known (at 10 K,  $H = 75$  kOe [2]). This fact facilitates the analysis of the spectra obtained for several sites of tin; (ii) the Néel point of  $\text{YCrO}_3$  ( $T_N = 141$  K [5]) is higher than that of  $\text{LuCrO}_3$  (111 K [6]) investigated previously as a matrix for  $^{119}\text{Sn}^{4+}$ . The higher value of  $T_N$  is an advantage in studying the samples which need *in situ* low-temperature measurements which cannot be carried out at 4.2 K. For instance, in the case of  $\text{YCrO}_3$ , a conclusion about the occurrence or non-occurrence of the spin polarization of  $\text{Sn}^{2+}$

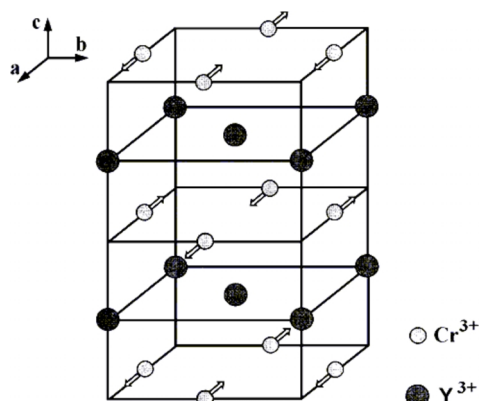


Fig. 1. Orthorhombic unit cell of  $\text{YCrO}_3$ . Only the  $\text{Cr}^{3+}$  and  $\text{Y}^{3+}$  sites are shown. The arrows indicate the directions of  $\text{Cr}^{3+}$  spin moments [5].

can already be drawn from the *in situ*  $^{119}\text{Sn}$  spectrum taken at 100 K; (iii) as the saturation value of  $H$  for  $\text{Sn}^{4+}$  in  $\text{YCrO}_3$  ( $H_{T \rightarrow 0\text{K}} = 75$  kOe [2]) is considerably higher than that for  $\text{LaCrO}_3$  ( $H_{T \rightarrow 0\text{K}} = 35$  kOe [2]), the former chromite appears to be preferable as a magnetic substrate, despite the much higher  $T_N$  of  $\text{LaCrO}_3$  (282 K [5]); (iv) the electronic shell of  $\text{Y}^{3+}$ , like that of both  $\text{Lu}^{3+}$  and  $\text{La}^{3+}$ , has no unpaired electrons. Hence, for the interpretation of magnetically split  $^{119}\text{Sn}$  spectra, only the interactions of the dopant with neighboring  $\text{Cr}^{3+}$  cations are to be considered for  $\text{YCrO}_3$  (Fig. 1).

## Experimental Section

To achieve better homogeneity of the dopant distribution in the sample, the procedure of synthesis involved a coprecipitation stage. To obtain an  $\text{YCr}(\text{OH})_6 \cdot x\text{H}_2\text{O}$  precursor, doped with 0.3 at.-% Sn, 9 mL of 10% aqueous ammonia solution was added to 40 mL of a hot acidified aqueous solution containing chromium (III) acetate (5.4 mmol), yttrium nitrate (5.4 mmol) and stannic chloride ( $1.62 \times 10^{-2}$  mmol) enriched to 92% with the isotope  $^{119}\text{Sn}$ . The precursor was filtered, washed with distilled water and dried in air at 130 °C.

An  $\text{YCrO}_3$  sample containing the  $^{119}\text{Sn}$  probe in the bulk of crystallites (sample 1) was prepared by calcining the precursor in air at 900 °C for 26 h. To obtain an  $\text{YCrO}_3$  sample with  $^{119}\text{Sn}$  cations located on the surface sites (sample 2), an acidified  $^{119}\text{SnCl}_4$  solution was dropped on a dopant-free  $\text{YCrO}_3$  powder substrate prepared under similar conditions. Prior to this treatment,  $\text{YCrO}_3$  was moistened with a 10% aqueous ammonia solution to promote fast hydrolysis of  $\text{SnCl}_4$  upon contact with  $\text{YCrO}_3$ . The overall composition of the samples 1 and 2 was the same (molar ratio  $[\text{Y}]:[\text{Cr}]:[\text{Sn}] = 1:1:0.003$ ). After being washed with water

and dried in air at 130 °C, the tin-impregnated powder was calcined in  $\text{H}_2$ , first in a quartz tube at 600 °C for 1 h and then, after being transferred to a quartz reactor, at 900 °C for 2 h. Using this reactor, which was equipped with a lateral thin quartz sample cell [7], a  $^{119}\text{Sn}$  spectrum could be taken after cooling the sample *in situ* in hydrogen atmosphere, *i. e.* out of contact with ambient air (the measurements are denoted hereafter as *in situ* Mössbauer spectroscopic measurements).

In all cases, XRD analysis of the resulting material revealed the presence of a single phase, an orthorhombically distorted  $\text{YCrO}_3$  perovskite (space group  $Pnma$  [8, 9]).

$^{119}\text{Sn}$  spectra were recorded using a conventional spectrometer operating in constant acceleration mode with a  $\text{Ca}^{119\text{m}}\text{SnO}_3$  source (all the isomer shift values  $\delta$  refer to the  $\text{BaSnO}_3$  absorber at 295 K). Spectra at 4.2 K were taken using a regular Oxford Instruments cryostat. The *in situ* Mössbauer spectroscopic measurements were performed at 295 and 100 K. To record a spectrum at 100 K, the cell filled with the studied material was mounted in the hole of a copper bar immersed in a liquid-nitrogen-filled Dewar flask. The spectra were analyzed using routine software.

XPS measurements were made using an ESCALAB VG 220i-XL spectrometer ( $\text{MgK}\alpha$  exciting radiation,  $h\nu = 1253.6$  eV) with powder samples pressed on indium supports. Atomic concentrations were calculated from the integrated intensities of the  $\text{Sn}3d5/2$  ( $E_b = 486.6$  eV),  $\text{Cr}2p3/2$  ( $E_b = 576.3$  eV) and  $\text{Y}3d5/2$  ( $E_b = 157.3$  eV) peaks. High-resolution spectra were fitted and quantified using the AVANTAGE software provided by ThermoFischer Scientific, each spectrum being referenced to the  $\text{Sn}3d5/2$  maximum at 486.6 eV.

## Results and Discussion

### *Mössbauer spectra of an $\text{YCrO}_3$ sample containing $^{119}\text{Sn}^{4+}$ in the bulk of crystallites (sample 1)*

The spectrum at 295 K (Fig. 2a) consists of a broadened peak whose isomer shift value ( $\delta = 0.08$  mm  $\text{s}^{-1}$ ) attests to the exclusively tetravalent nature of Sn. The significantly larger value of the width at half maximum ( $\Gamma = 1.15$  mm  $\text{s}^{-1}$ ), as compared to that of a reference  $\text{BaSnO}_3$  sample ( $\Gamma_{\text{ref.}} = 0.90$  mm  $\text{s}^{-1}$ ), is due to weak quadrupole interactions of  $^{119}\text{Sn}^{4+}$  in the distorted perovskite structure of  $\text{YCrO}_3$ . The average value of the quadrupole splitting  $E_Q = 0.35$  mm  $\text{s}^{-1}$  (Table 1), corresponding to the observed  $\Gamma$  value, is in qualitative agreement with the value  $E_Q = 0.46$  mm  $\text{s}^{-1}$  [3] reported for  $\text{Sn}^{4+}$  in the somewhat more distorted structure of  $\text{LuCrO}_3$ .

At 4.2 K, a complex pattern of Zeeman splitting appears in the  $^{119}\text{Sn}$  spectrum (Fig. 2b) which attests to the spin polarization of the electronic shell of  $\text{Sn}^{4+}$

Table 1. Mössbauer-spectroscopic parameters of the  $^{119}\text{Sn}$  probe located in the bulk (sample **1**) and on the surface (samples **2** and **2<sub>ox</sub>**) of  $\text{YCrO}_3$  polycrystals.

$T$ , K	$\delta$ (mm s $^{-1}$ )	$E_Q$ (mm s $^{-1}$ )	$\Gamma$ (mm s $^{-1}$ )	$H$ (kOe)	$A$ (%)
Sample <b>1</b> :					
295	$0.08 \pm 0.03$	$0.35 \pm 0.05$	$0.90 \pm 0.05$	–	100
4.2	$0.11 \pm 0.05$		$1.0 \pm 0.1$	$80 \pm 3$	$68 \pm 5$
	$0.11 \pm 0.05$		$1.0 \pm 0.1$	$47 \pm 5$	$12 \pm 5$
	$0.11 \pm 0.05$		$1.0 \pm 0.1$	$17 \pm 5$	$12 \pm 5$
	$0.11 \pm 0.05$		$1.0 \pm 0.1$	$122 \pm 5$	$8 \pm 5$
Sample <b>2</b> ( <i>in situ</i> measurements):					
295	$2.76 \pm 0.04$	$1.95 \pm 0.06$	$1.0 \pm 0.1$	–	$86 \pm 10$
	$\sim 0$				$14 \pm 5$
100	$2.82 \pm 0.04$	$1.97 \pm 0.06$	$1.1 \pm 0.1$	–	$90 \pm 5$
	$\sim 0$				$10 \pm 5$
Sample <b>2<sub>ox</sub></b> (after exposure of sample <b>2</b> to air):					
295	$0.06 \pm 0.04$	$0.6 \pm 0.1$	$1.1 \pm 0.1$	–	$90 \pm 10$
	$2.8 \pm 0.1$	$2.0 \pm 0.1$	$1.0 \pm 0.1$	–	$10 \pm 5$
4.2	$0.15 \pm 0.05$	$0.7 \pm 0.1$	$1.0 \pm 0.1$	–	$70 \pm 5$
	$0.15 \pm 0.05$		$1.1 \pm 0.1$	$35 \pm 8$	$15 \pm 5$
	$2.8 \pm 0.1$	$2.0 \pm 0.1$	$1.1 \pm 0.1$	–	$15 \pm 5$

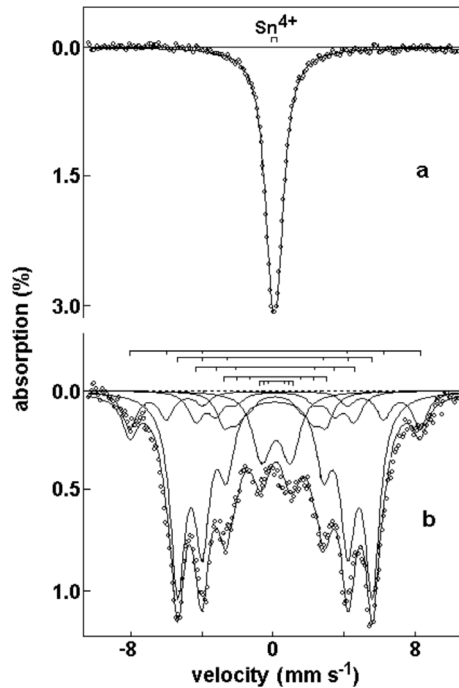


Fig. 2.  $^{119}\text{Sn}$  Mössbauer spectra of sample **1**;  $T_{\text{meas}} = 295$  K (a) and 4.2 K (b).

below  $T_N$ . The analysis of the spectrum shows that it can be represented by a superposition of a number of subspectra with different values of  $H$  (Table 1). The predominant contribution arises from the subspectrum corresponding to  $H = 80$  kOe. This value is in close

agreement with that reported in [2] for  $\text{Sn}^{4+}$  ions on the  $\text{Cr}^{3+}$  site in the bulk of  $\text{YCrO}_3$  (at 10 K,  $H = 75$  kOe). It should be noted that the sample studied in [2] was synthesized by annealing a mixture of  $\text{Y}_2\text{O}_3$  and  $\text{Cr}_2\text{O}_3$  which contained, besides the  $^{119}\text{SnO}_2$  additive, an equimolar amount of  $\text{CaO}$  to compensate the  $\text{Sn}^{4+}$  excess charge. So, the absence in [2] of any allusion to the occurrence of various  $^{119}\text{Sn}$  subspectra allows us to account for the complexity of the spectrum in Fig. 2b by another  $\text{Sn}^{4+}$  charge compensation mechanism in the  $\text{Ca}^{2+}$ -free chromite structure. In fact, as the  $\text{Cr}^{3+}$  moments exhibit a G-type AF arrangement [10], each  $\text{Cr}^{3+}$  (and its isolated  $\text{Sn}^{4+}$  substituent) possesses, in this compound, six  $\text{Cr}^{3+}$  neighbors with parallel spins. This means that the partial contribution  $h$  from one neighboring  $\text{Cr}^{3+}$  to the effective  $H$  value at 4.2 K is expected to be *ca.* 13 kOe. Therefore, if the compensation of the  $\text{Sn}^{4+}$  excess charge in  $\text{YCrO}_3$  involves the creation of vacancies  $V_{\text{Cr}^{3+}}$ , as it was the case in  $\text{Cr}_2\text{O}_3$  [11], some  $\text{Sn}^{4+}$  and  $V_{\text{Cr}^{3+}}$  sites may lead to the segregation of point defects. The  $\text{Sn}^{4+}$  ions concerned will thus possess a reduced number of magnetic neighbors, and new spectral components with lower values of  $H$  and multiples of 13 kOe will appear in the  $^{119}\text{Sn}$  spectra. This expectation is in qualitative agreement with the data of a computer analysis of the spectrum of sample **1** at 4.2 K (Table 1). However, it is quite obvious that such segregations of point defects do not allow one to account for the presence of a sextet with  $H \sim 120$  kOe, significantly greater than 80 kOe. On the contrary, the occurrence may be explained assuming that the compensation of the excess charge of some  $\text{Sn}^{4+}$  ions involves the formation of  $V_{\text{Y}^{3+}}$  yttrium vacancies. In fact, the appearance of  $V_{\text{Y}^{3+}}$  in the nearest surrounding of  $\text{Sn}^{4+}$  can change the average value of the angles  $\theta$  of the concerned  $\text{Cr}(\text{Sn})\text{-O-Cr}$  superexchange pathways. It was shown [2] that, with a decreasing ionic radius  $r$  of  $R^{3+}$ , the  $\theta$  value decreases, and the  $\pi$  bonding (responsible for the spin polarization of  $\text{Sn}^{4+}$ ) increases. Consequently, an increase of the  $H$  value is observed with decreasing  $r$ . Therefore, if there is a  $V_{\text{Y}^{3+}}$  vacancy in the vicinity of  $\text{Sn}^{4+}$  (which corresponds to the substitution of  $\text{Y}^{3+}$  for an atom with  $r = 0$ ), the *local* average  $\theta$  value is expected to be lower than  $144.9^\circ$ , the value reported in [12] for undoped  $\text{YCrO}_3$ . It has been shown [2, 13] that the dependence of  $H$  on  $\theta$  may be approximated by a linear relation  $H = a_0 + a_1 \cos^2 \theta$  with  $a_0 = 240$  kOe and  $a_1 = -254$  kOe. Accordingly, for the  $\text{Sn}^{4+}$  ions concerned

the value of  $H = 120$  kOe would correspond to the *local* average value of  $\theta = 140^\circ$ .

*Mössbauer spectra of a tin-doped  $\text{YCrO}_3$  containing  $\text{Sn}^{2+}$  on the surface of its crystallites (sample 2)*

The *in situ*  $^{119}\text{Sn}$  spectrum, recorded at 295 K after  $\text{H}_2$  annealing of the tin-impregnated  $\text{YCrO}_3$  sample (sample 2), consists mainly of a quadrupole doublet and a weak residual absorption near  $\nu \sim 0$  mm s $^{-1}$  (Fig. 3a). Both the  $\delta = 2.76 \pm 0.04$  mm s $^{-1}$  and  $E_Q = 1.95 \pm 0.06$  mm s $^{-1}$  values, relative to the doublet (Table 1), are in fair agreement with those reported for  $\text{Sn}^{2+}$  ions on surface sites of  $\text{LuCrO}_3$  ( $\delta = 2.74$  mm s $^{-1}$  and  $E_Q = 1.94$  mm s $^{-1}$  [3]). The weak absorption observed near  $\nu = 0$  mm s $^{-1}$  attests to the presence of  $\text{Sn}^{4+}$  ions and thus points to the presence of a small amount of tin in the bulk of  $\text{YCrO}_3$ . An accurate determination of other Mössbauer spectrometric parameters of this component is prohibited by its too low spectral contribution.

According to [14], the features of the spectrum at 295 K clearly demonstrate the location of the large majority of tin ions on the surface of the crystallites. In

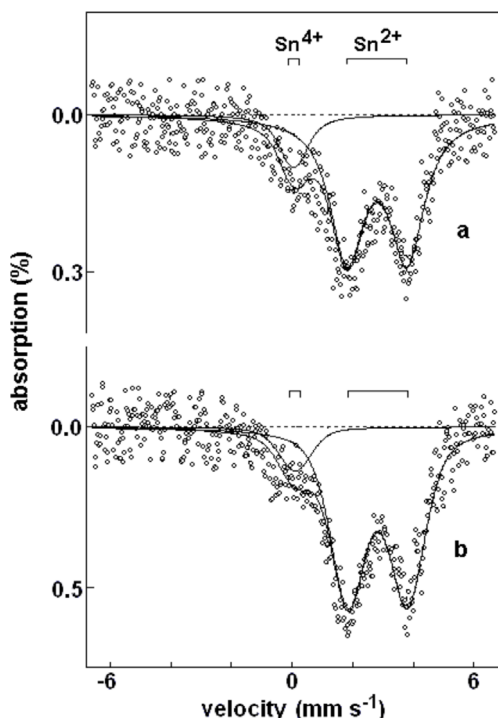


Fig. 3.  $^{119}\text{Sn}$  Mössbauer spectra of sample 2, recorded *in situ* in  $\text{H}_2$ ;  $T_{\text{meas}} = 295$  K (a) and 100 K (b).

fact, once  $\text{Sn}^{4+}$  ions appear at the interface, they are easily reduced by  $\text{H}_2$  to the divalent state and, due to hybridized  $\text{Sn}^{2+}$  ( $5s5p$ ) lone pair electrons, can occupy available low-coordination sites energetically unfavorable for  $\text{Cr}^{3+}$  and  $\text{Y}^{3+}$ . So the presence of  $\text{Sn}^{2+}$  diminishes the number of surface-located coordinatively unsaturated  $\text{Cr}^{3+}$  and  $\text{Y}^{3+}$  ions which results in the anomalously high stability of  $\text{Sn}^{2+}$  ions with respect to their further reduction to the metallic state. The surface localization of  $\text{Sn}^{2+}$  thus allows one to account for the at first glance surprising absence, in Fig. 3a, of the single-line peak of  $\beta$ -Sn (with  $\delta = 2.56$  mm s $^{-1}$ ), despite an  $\text{H}_2$ -annealing temperature as high as 900 °C. Finally, the surface-location of  $\text{Sn}^{2+}$  is in fair agreement with the results of an XPS analysis of the air-contacted sample 2. The atomic ratio  $\frac{[\text{Sn}]}{[\text{Cr}+\text{Y}]}$  for a 2–3 nm thick surface layer is found to be 0.16. This value is about 100 times larger than the overall ratio calculated on the basis of the quantities of the reagents involved in the synthesis ( $\frac{[\text{Sn}]}{[\text{Cr}+\text{Y}]} = 0.0015$ ).

The most interesting feature of the *in situ* spectrum at  $T \sim 100$  K (Fig. 3b) is the fact that the peaks of the  $\text{Sn}^{2+}$  ions exhibit no Zeeman splitting, despite the rather low value of  $\frac{T}{T_N} \sim 0.7$ . The lack of spin polarization means that the  $\text{Sn}^{2+}$  ions possess a magnetically inactive surrounding and, consequently, an antiparallel orientation of the spins of their different  $\text{Cr}^{3+}$  neighbors. This conclusion is corroborated by Mössbauer spectroscopic measurements after a short-term exposure of sample 2 to air (sample 2<sub>ox</sub>). In fact, the spectrum of sample 2<sub>ox</sub> at 295 K (Fig. 4a) reveals a rapid re-oxidation of the main part of the  $\text{Sn}^{2+}$  ions. This reaction probably involves only the attachment of an oxygen atom to the lone pair of electrons of a surface-located  $\text{Sn}^{2+}$ , without any significant change in the *cationic* surrounding of the oxidized  $\text{Sn}^{4+}$ . The validity of such an assumption has been experimentally proven for tin ions on the surface of  $\text{Cr}_2\text{O}_3$  [15].

The comparison of the  $H$  values of  $\text{Sn}^{4+}$  ions located on sites with known surroundings in the bulk of  $\text{YCrO}_3$  (sample 1) with the  $H$  values relative to the “daughter” ( $\text{Sn}^{2+} \rightarrow \text{Sn}^{4+}$ ) ions produced on the surface (sample 2<sub>ox</sub>) reveals the peculiarities of the cation surroundings of the surface-located cations. The  $^{119}\text{Sn}$  spectrum of sample 2<sub>ox</sub> at 4.2 K is shown in Fig. 4b. It suggests the presence of two kinds of  $\text{Sn}^{4+}$  ions. The large majority of them (Table 1) occupies sites with a magnetically inactive surrounding. Taking into account

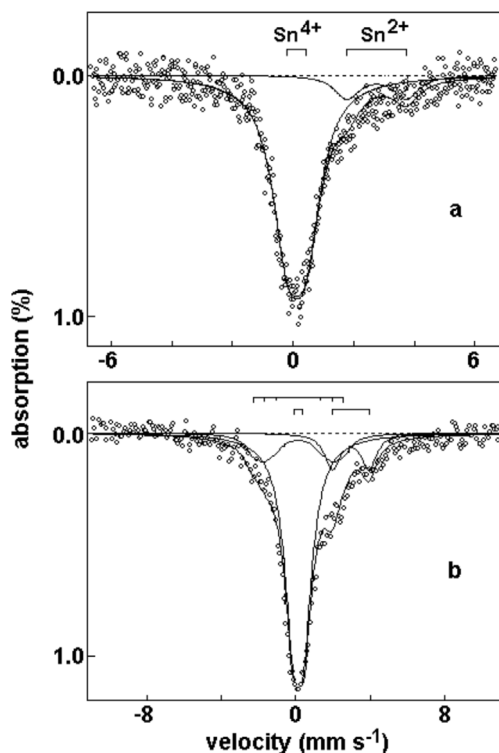


Fig. 4.  $^{119}\text{Sn}$  Mössbauer spectra of sample  $2_{\text{ox}}$ ;  $T_{\text{meas}} = 295$  K (a) and 4.2 K (b).

the very low value of  $\frac{T}{T_N} = 0.03$ , this conclusion seems to be quite obvious. Consequently, on the surface, contrary to the bulk, the magnetically inactive  $\text{Y}^{3+}$  sites are mainly occupied by both the daughter  $\text{Sn}^{4+}$  and parent  $\text{Sn}^{2+}$  ions, in agreement with the lack of magnetic splitting in Fig. 3b.

However, as can be seen in Fig. 4b, a certain amount of spin-polarized  $\text{Sn}^{4+}$  ions ( $H = 35 \pm 5$  kOe) is nevertheless present in sample  $2_{\text{ox}}$ . As mentioned above, the sextet with  $H = 80$  kOe represents  $\text{Sn}^{4+}$  on a  $\text{Cr}^{3+}$  bulk site possessing six  $\text{Cr}^{3+}$  neighbors. The spectral component with  $H = 35$  kOe (Fig. 4b) is therefore to be at-

tributed to  $\text{Sn}^{4+}$  located on surface  $\text{Cr}$  sites possessing only three  $\text{Cr}^{3+}$  neighbors. The lower value of  $H$  for the “daughter”  $\text{Sn}^{4+}$  ions concerned accounts for the lack of noticeable magnetic splitting for the “parent”  $^{119}\text{Sn}^{2+}$  cations at 100 K (*cf.* Fig. 3b). In fact, contrary to the case of  $\text{Sn}^{4+}$ , the  $5s$  orbitals of  $\text{Sn}^{2+}$  are formally filled. So, the  $3d$ - $5s$  transfer of spin density from  $\text{Cr}$  to  $\text{Sn}$  is strongly impeded for  $\text{Sn}^{2+}$ . This leads to a drastic decrease of the spin polarization of  $\text{Sn}^{2+}$  as compared to  $\text{Sn}^{4+}$ . For instance, the  $H$  value was found to be 2.5 times lower for  $\text{Sn}^{2+}$  on the surface of  $\text{Cr}_2\text{O}_3$  [15] and about 13 times lower for  $\text{Sn}^{2+}$  in the bulk of  $\alpha$ - $\text{MnS}$  (containing both  $\text{Sn}^{2+}$  and  $\text{Sn}^{4+}$  ions on the sites with a similar cationic surrounding) [16]. Accordingly, for the value of 35 kOe, relative to the “daughter”  $\text{Sn}^{4+}$  (sample  $2_{\text{ox}}$ ), a value of  $H$  ranging from 14 to 3 kOe is to be anticipated at 100 K for the parent  $^{119}\text{Sn}^{2+}$  (sample  $2$ ). Such magnetic fields are too weak to noticeably affect the shape of a composite spectrum comprising a much more intense pure quadrupole doublet with very similar Mössbauer spectroscopic parameters.

## Conclusions

The location of  $\text{Sn}^{4+}$  ions (0.3 at.-%) on  $\text{Cr}^{3+}$  sites in the bulk of  $\text{YCrO}_3$  is shown to involve the formation of charge compensation vacancies of both chromium ( $V_{\text{Cr}^{3+}}$ ) and yttrium ( $V_{\text{Y}^{3+}}$ ). The occurrence of  $V_{\text{Cr}^{3+}}$  in the nearest cationic surrounding of  $\text{Sn}^{4+}$  decreases its spin polarization while the presence of  $V_{\text{Y}^{3+}}$  has the opposite effect. Upon annealing in  $\text{H}_2$ , reduction of  $\text{Sn}^{4+}$  to  $\text{Sn}^{2+}$  and stabilization of the latter on the surface sites becomes evident. The lack of spin polarization for the large majority of the  $\text{Sn}^{2+}$  ions at 4.2 K points to their location on  $\text{Y}^{3+}$  sites.

## Acknowledgement

This work was supported by the Russian Foundation for Basic Research (Grant RFBR No 10-03-0002).

- [1] V. A. Bokov, G. V. Popov, N. N. Parfenova, G. G. Yushina, *Fizika Tverdogo Tela* **1972**, *14*, 104–108.
- [2] N. S. Ovanesyan, V. A. Trukhtanov, *Proceedings of the Fifth International Conference on Mössbauer Spectroscopy*, Prague, Part 1, **1975**, pp. 157–161.
- [3] M. I. Afanasov, A. Wattiaux, C. Labrugère, P. B. Fabritichnyi, C. Delmas, *Solid State Commun.* **2009**, *149*, 1333–1336.
- [4] K. Rida, A. Benadbas, F. Bouremmad, M. A. Pena, A. Martinez-Arias, *Catalysis Commun.* **2006**, *7*, 963–968.
- [5] E. F. Bertaut, G. Bassi, G. Buisson, P. Burlet, J. Chappert, A. Delapalme, J. Mareschal, G. Roullet, R. Aléonard, R. Pauthenet, J. P. Rebouillat, *J. Appl. Phys.* **1966**, *37*, 1038–1039.

- [6] R. M. Hornreich, S. Shtrikman, B. M. Wanklyn, I. Yaeger, *Phys. Rev. B* **1976**, *13*, 4046–4052.
- [7] I. S. Bezverkhy, Dissertation, Moscow State University, Moscow, **1998**.
- [8] S. Geller, E. A. Wood, *Acta Crystallogr.* **1956**, *9*, 563–568.
- [9] K. Ramesha, A. Llobet, Th. Proffen, C. N. R. Rao, *J. Phys.: Condens. Matter.* **2007**, *19*, 102202.
- [10] J. B. Goodenough, *Rep. Prog. Phys.* **2004**, *67*, 1915–1993.
- [11] P. B. Fabritchnyi, L. P. Fefilatiev, *Solid State Commun.* **1978**, *28*, 513–515.
- [12] K. Motida, S. Miyahara, *Phys. Soc. Japan.* **1970**, *28*, 1188–1196.
- [13] I. S. Lyubutin, T. V. Dmitrieva, A. S. Stepin, *Zh. Eksp. Teor. Fiz.* **1999**, *115*, 1070–1084.
- [14] P. B. Fabritchnyi, M. I. Afanasov, M. Danot, *Russ. J. General Chem.* **2008**, *78*, 1060–1069.
- [15] M. I. Afanasov, M. Danot, A. A. Ryabchikov, S. Maingaud, P. B. Fabritchnyi, J. Rouxel, *Mater. Res. Bull.* **1996**, *31*, 465–474.
- [16] M. Danot, V. E. Tkachenko, K. V. Pokholok, S. Maingaud, P. B. Fabritchnyi, J. Rouxel, *Mater. Res. Bull.* **1995**, *30*, 563–571.