



HAL
open science

Identification of finite shear-elasticity at low thickness in the liquid state of molecular (OTP) and polymeric glass formers (PBUA)

Laurence Noirez, Patrick Baroni, Hakima Mendil-Jakani

► To cite this version:

Laurence Noirez, Patrick Baroni, Hakima Mendil-Jakani. Identification of finite shear-elasticity at low thickness in the liquid state of molecular (OTP) and polymeric glass formers (PBUA). *Philosophical Magazine*, 2011, pp.1. 10.1080/14786435.2010.536176 . hal-00670239

HAL Id: hal-00670239

<https://hal.science/hal-00670239>

Submitted on 15 Feb 2012

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Identification of finite shear-elasticity at low thickness in the liquid state of molecular (OTP) and polymeric glass formers (PBUA)

Journal:	<i>Philosophical Magazine & Philosophical Magazine Letters</i>
Manuscript ID:	TPHM-10-Jun-0269.R1
Journal Selection:	Philosophical Magazine
Date Submitted by the Author:	19-Oct-2010
Complete List of Authors:	Noirez, Laurence; Laboratoire Léon Brillouin Baroni, Patrick; Laboratoire Léon Brillouin, CE-Saclay Mendil-Jakani, Hakima; CEA, SprAM
Keywords:	surfaces, tribology, wetting, solid solutions, soft matter
Keywords (user supplied):	solid-like correlations, liquid state

SCHOLARONE™
Manuscripts

Identification of finite shear-elasticity at low thickness in the liquid state of molecular (OTP) and polymeric glass formers (PBuA)

L. Noirez¹, H. Mendil-Jakani², P. Baroni¹

¹Laboratoire Léon Brillouin (CEA-CNRS), CE-Saclay, 91191 Gif-sur-Yvette Cédex, France

²Current address : Structure et Propriétés d'Architectures Moléculaires, UMR 5819 SPrAM (CEA-CNRS-UJF), CEA-Grenoble, 17, avenue des Martyrs, 38054 Grenoble, cedex 9, France.

*Correspondance to: Laurence Noirez

E-mail: laurence.noirez@cea.fr

(Received XX Month Year; final version received XX Month Year)

Finite shear elasticity has been identified in the liquid state. The study is expanded to a van der Waals molecular glass former, the o-Terphenyl and to an ordinary polymer melt, the polybutylacrylate as a function of its molecular weight. These fluids exhibit elasticity at the sub-millimeter scale and far above any phase transition. This macroscopic property challenges the conventional terminal relaxation modes (α -process or reptation times) in terms of individual molecular process.

Keywords: glass formers, liquid state, elastic properties.

1. Introduction

To define three states of matter such as solid, liquid or glass and the transitions between them, the shear and bulk moduli are certainly of the most useful and relevant characteristic features[1]. The shear modulus presents a substantial advantage over the bulk modulus because a specific instrumentation has been elaborated to routinely measure the dynamic properties of viscoelastic materials (materials displaying dynamic behaviours intermediate between liquid and solid). These apparatus are dynamic mechanical analysers, rheometers, shear resonators, surface force apparatus... Based on the same principle, these devices measure the stress or the motion transmitted by simple contact between the sample and the surface submitted to small mechanical oscillatory solicitations. This mechanical technique is currently the only one able to probe long time scales.

The boundary conditions between the surface and the sample play a major role in this measurement since the efficiency of the transmission of the motion, and thus in the quality of the measurement are completely dependent on the interaction between the surface and the material. Up-to-date progresses in the sensitivity of the instrumentation and in the techniques allow the access to the measurement of the shear modulus with a high precision and over 6 decades of magnitude. These improvements have considerably widened the frequency window and the modulus range, and therefore enable the detection of subtle properties that would not been considered before. Recent developments have shown that it is also possible to improve significantly the measurement by controlling the boundary conditions between the material and the substrate whereby the stress and the measurement are transmitted[2]. Using this method, a protocol has been established to measure elastic properties at the sub-millimetre scale in the liquid state of various materials as glass formers (Glycerol, PPG,

1
2
3 presently o-Terphenyl) but also polymer melts so far considered as viscous liquids far away
4 from any phase transition[3,4]. These results showing that the shear modulus in liquids is not
5 zero, contrast with the conventional macroscopic description. The solid-like property is
6 usually not considered since this delicate signal mostly observable at low thickness geometry
7 is hidden in conventional mechanical measurements. However, new studies and results
8 emerging from different disciplines as microrheology[5], dielectric relaxation[6], NMR [7],
9 X-ray photon correlation spectroscopy[8], voltage effects[9] evidence relaxation modes much
10 slower than those described in conventional theoretical models. It points out that a pure
11 viscous approach of the liquid state as adopted for example to interpret the phenomenology of
12 the supercooling formation and of the glass transition cannot be satisfying. The consideration
13 of this non-negligible macroscopic component is of first importance to redefine the relevant
14 parameters for a better understanding of glass and glass former properties and more generally,
15 of the fluid properties.
16

17 In this paper, a new series of experimental results is presented illustrating the
18 measurement of a finite shear modulus in the liquid state of two Van der Waals glass formers.
19 The first one, the o-Terphenyl (OTP) is a molecular glass former. It displays a melting point
20 at 56°C and a glass transition temperature at about -30°C[10]. Classified as a fragile glass
21 former (the viscosity is not obeying to Arrhenius temperature dependence in the supercooled
22 state), the o-Terphenyl crystallises from the supercooled state at around 35°C when it is
23 slowly cooled down. The crystallisation can be prevented by a rapid cooling of the melt,
24 giving rise to an amorphous glass below the glass transition temperature. The non or delayed
25 crystallisation properties are due to the no-planarity of the molecule because of the short
26 distances between non-bonded carbon atoms[11]. The other studied material, the
27 polybutylacrylate (PBuA), is a polymeric Van der Waals glass former. The polybutylacrylate
28 is an amorphous material characterised only by a glass transition temperature ($T_g = -64^\circ\text{C}$) and
29 therefore does not display any supercooled state. Its molecular weight is a variable parameter
30 and its influence on the shear modulus will be examined. Finally, the concept of terminal
31 relaxation time of polymers (reptation time for entangled polymers and Rouse time for
32 unentangled chains) deduced from conventional viscoelastic measurements will be discussed.
33 Similarly, the *alpha* process, the slowest relaxation mode in molecular liquids as the OTP,
34 corresponding roughly to molecular rotation[12] will be examined. This mode is usually not
35 accessible via mechanical measurements. This dynamics is typically characterised by
36 dielectric spectroscopy[13], dynamic light scattering [14], NMR [15], quasi-elastic neutron
37 scattering [16] (the cited references are related to the OTP).
38
39
40
41
42

43 2. Experimental

44
45 o-Terphenyl was purchased from Aldrich (99% purity). It presents a glass transition at
46 about $-30^\circ\text{C} \pm 1^\circ\text{C}$ and a melting point at 56°C (see Table 1). The working temperatures are
47 ranging from 54.6°C up to 100°C, thus mainly above the melting point and some slightly
48 below it. The polymer is an ordinary polybutylacrylate of well-defined molecular weight. The
49 series of different molecular weight monodisperse PolyButylacrylate was purchased from
50 Polymer Source (Table 1). Its glass transition temperature is -64°C. The working temperature
51 is the room temperature. Before the experiment, the samples were observed by optical
52 microscopy (to ensure the absence of air bubbles) and maintained under vacuum before the
53 experiment. The sample is deposited between two disk-like alumina surfaces freshly cleaned
54 by thermal treatment (400°C). The two surfaces are approached until the full contact with the
55 liquid is achieved.
56
57
58
59
60

1
2
3 The experiments are carried out using a dynamic mechanical analyser (ARESII, TA-
4 Instruments) following the protocol described in [2-4] to improve the dynamic response and
5 determine the non-vanishing low frequency shear modulus. The room is equipped with an air
6 conditioning and the temperature on the sample is ensured with an air pulsed oven ensuring a
7 thermal stability of less than $\pm 0.1^\circ\text{C}$. The zero gap is set by contact; the error is positive and
8 less than 0.005mm. The measurement consists in applying a constant shear strain of amplitude
9 (γ) to the sample by imposing a small oscillation of variable frequency (ω) on one disk (strain
10 imposed mode). The second disk is immobile and coupled with a transducer on its central
11 axis. It measures the torque (σ) transmitted by the material under solicitation. The moduli are
12 classically extracted from the difference between the input and the output signals; the
13 component in phase with the strain determines the elastic (or storage) modulus (G'), whereas
14 the out of phase component defines the viscous (or loss) modulus (G'') following the
15 relationship: $\sigma(\omega) = \gamma_0.(G'(\omega).\cos(\omega t) + G''(\omega).\sin(\omega t))$. The representation of $G'(\omega)$ and
16 $G''(\omega)$ versus frequency provides the dynamic signature of the material and points out its
17 eigen modes. A typical relaxation mode (reptation time) in polymeric liquids (melt and
18 solutions) is given by the interception of G' and G'' that signs the slowest relaxation time
19 before entering in the low frequency flow regime.
20
21
22
23

24 3. Results

25
26 The validity of a dynamic relaxation experiment is entirely depending on the
27 efficiency of the transmission of the motion by contact between the sample and the surfaces
28 (fixtures). Because of symmetry reasons, surface properties differ from the 3D properties. The
29 ideal boundary conditions should exhibit an energy at the frontier between these two
30 homogeneous media as low as possible; in other words, the surface energy has to be as high
31 as possible. A good criterion is the observation of a total wetting of the fluid onto the
32 substrate[17]. This is achieved for example by employing zero porosity alumina substrates[2].
33 The use of total wetting substrate reinforces the liquid/substrate interaction, and prevents the
34 slippage[18]. Using the total wetting boundary conditions, we have already shown that it is
35 possible to improve the dynamic response and to reveal a non-vanishing low frequency shear
36 modulus far above the glass transition in various viscous liquids[3,4]. This measurement
37 protocol is here applied to the liquid state of a glass former, the o-Terphenyl and to an
38 amorphous polymer, the polybutylacrylate in the molten state at temperatures far away from
39 the glass transition.
40
41
42

43 Fig.1a displays the response of the o-Terphenyl above the melting point, at $+7.7^\circ\text{C}$
44 above T_m and $45\mu\text{m}$ gap thickness. The upper points of the figure indicates a solid-like
45 response; the shear modulus G' is independent of the frequency within this observation
46 window (which is the conventional frequency range). These results have been obtained at low
47 strain amplitude using total wetting surfaces. These surfaces made of alumina with zero
48 porosity are characterised by a low roughness number [2] and wide flat zones at the atomic
49 scale as shown in the upper photograph (Fig.1b). The bottom photograph illustrates the
50 geometry of the experiment, the dimensions and the quality of the parallelism between
51 surfaces spaced by a $45\mu\text{m}$ gap thickness. The transmission of the light through the sample
52 guaranties the absence of any contact that could explain the solid-like behaviour above T_m
53 and points out the macroscopic character of the probed property. This protocol reveals long
54 range elastic cohesive correlations in a glass former so far considered as purely viscous in the
55 liquid state.
56
57
58
59
60

1
2
3 The data symbolized by opened circles in Fig.1a are obtained at very high strain
4 amplitude ($\gamma=1000\%$). Only the viscous modulus is presented, the shear modulus being
5 below the limit of resolution of the device. This behaviour was already observed and
6 illustrated in [3,4] for Glycerol and ordinary polymer melts. It shows the fragility of the solid-
7 like response with respect to the strain parameter and also the experimental difficulty to
8 access to this primary elastic regime. At high strain amplitude, the viscous modulus follows
9 the conventional ω -scale behaviour the slope of which indicating the dynamic viscosity ($G'' =$
10 $\eta \cdot \omega$). The estimated value ($\eta = 0.011\text{Pa}\cdot\text{s}$ at 64°C and $45\mu\text{m}$) is in agreement with the usual
11 tabulated values [19].

12
13 On Fig.1c, we detail the strain induced transition from solid-like to viscous behaviour,
14 showing separately its effect on the shear and on the viscous moduli. The right inset gathers
15 the results at 10rad/s . These measurements have been carried out at the same temperature as the data
16 of Fig.1a, but at a lower thickness ($25\mu\text{m}$). The moduli in the linear regime are higher in agreement
17 with the gap evolution presented in Fig.1d. The increase of the strain amplitude produces a
18 lowering of the terminal elasticity which is progressively replaced by the “conventional”
19 behaviour. At high strain and in the high frequency zone (typically above 5 rad/s), the viscous
20 modulus does not evolve anymore with the strain amplitude (see Fig.1a and Fig.1c) exhibiting
21 the onset of the conventional viscous curve scaling as ω .

22
23 Fig.1d displays the evolution of the shear modulus of the o-Terphenyl as a function of
24 the gap thickness. As already observed on other materials, the low frequency elasticity is
25 accessible at small gaps only, dependent on the gap thickness and typically measurable for
26 sample thicknesses lower than $50\text{-}100\mu\text{m}$. At higher gap thickness, the conventional
27 behaviour is recovered exhibiting the usual viscous law, similarly to what is observed at very
28 high strain amplitudes.

29
30 The second series of measurements with the o-Terphenyl starts from the supercooled
31 state. Fig.1e displays data obtained at $T = T_m - 1.4^\circ\text{C}$; the predominant elastic character is
32 also established in the supercooled phase. The solid-like response seems to be reinforced
33 compared to values obtained above T_m . The thermal evolution of the elasticity is displayed in
34 the inset of Fig.1e. The low temperature range is hardly accessible since the instrument can be
35 damaged if a crystallisation occurs after long equilibration times or is induced by applying
36 weak strain stresses. At high temperature, the measurement is limited by the balance between
37 the acquisition time and the evaporation time.

38
39
40 The same experimental protocol is applied to polymer melts. Fig.2a illustrates the
41 dynamic behaviour at 90°C above T_g , of a polybutylacrylate of molecular weight ($M_w =$
42 47500). This value indicates that the melt is in its entanglement regime ($Me = 22000$). The
43 study of unentangled polymers has been already considered in [20]. A particular change of
44 dynamic behaviour is observed as the chain length increases. This change is attributed to the
45 occurrence of an entanglement regime above a critical molecular weight $M^* = 2 \cdot Me$, where
46 Me is the molecular weight between entanglements. Below M^* , the viscosity varies almost
47 linearly with the chain length and no viscoelastic plateau is observed in the dynamic response.
48 Over M^* , the viscosity obeys to scaling laws with the molecular weight, and the dynamic
49 relaxation response displays a high frequency elastic plateau called “entanglement plateau” or
50 “rubbery plateau”[21, 22, 23]. At low frequency (terminal regime), both (entangled and
51 unentangled) melts of polymer display a flow behaviour characterised by a continuous
52 decrease of both elastic and viscous moduli ($G' \propto \omega^2$, $G'' \propto \omega$). Using the total wetting
53 protocol, Fig.2a shows that a terminal elasticity is observable at low gap thickness. This
54 measurement has been carried out at $25\mu\text{m}$ but the elasticity remains observable at larger gaps
55 as illustrated in Fig.2b. In all cases, the length scales probed correspond to macroscopic
56
57
58
59
60

1
2
3 dimensions that are several orders higher than the molecular dimensions and thus, the
4 elasticity has to be considered as the result of long range intermolecular interactions.

5 The evolution of the shear modulus is displayed from 0.025mm up to 0.500mm on
6 Fig.2b. The terminal elastic mode is visible for all these sample thicknesses. It is reinforced
7 by decreasing the gap thickness and disappearing by increasing the gap below the device
8 resolution. At high thickness (above 0.5mm – 1mm for polymer melts), the conventional
9 viscoelastic spectrum is restored displaying the typical flow behaviour. The low frequency
10 elasticity measured in the polymer melt is several decades higher and extended to larger
11 thicknesses compared to the o-Terphenyl. The reinforcement of the elasticity in polymers
12 indicates strongly that its origin is linked to long range intermolecular interactions.

13 The dependence with the thickness is not trivial and cannot be strictly restricted to a
14 surface effect since the length scales are largely above several molecular lengths. The increase
15 of the volume of the sample is concomitant with the increase of voids, of freedom degrees.
16 Since the transducer measurement is obtained by transmission over the sample thickness (it is
17 a transmission measurement), increasing dissipative contributions (self-diffusion, voids,
18 mobility...) may explain the lowering of the elasticity. Analogies with scaling mechanical
19 properties can be found with cements and foams[24, 25].

20 Since at low gap, unentangled melts [4] and molecular glass formers display a terminal
21 elasticity, entanglements are thus not at the origin of the rubbery plateau. How to relate this
22 terminal elasticity to the rubbery plateau? Fig.2c displays the evolution of the shear elasticity
23 as a function of the molecular weight.

24 Unentangled polymers ($M_w < M^*$) display an elasticity that increases rapidly with the
25 molecular weight up to M^* (Fig.2c, yellow part). Beyond ($M_w > M^*$), the elastic modulus
26 does not increase significantly and saturates at a rather constant value of about $G' \approx 8.10^4$ Pa.
27 This value merges with the ordinary rubbery plateau $G' = G_N^0$ [20]. Moreover, the transition
28 between these two regimes seems to coincide with the occurrence of the entanglement regime;
29 i.e. $M^* = 2.Me$ ($2.Me = 44000$ for the PBuA [20]). In the frame of these results pointing out
30 that the notion of flow behaviour becomes elusive at low thickness because replaced by a
31 terminal elasticity, it is emphasized that the notion of entanglement and of “entanglement
32 plateau” is also relative and cannot be simply interpreted in molecular terms. Clearly the
33 terminal elasticity, identified in both simple liquid glass formers and from low to high
34 molecular weight polymer melts is a condensed matter property.

35 36 37 38 39 40 41 **4. Conclusions - Discussions**

42 This study of the o-Terphenyl and of entangled polymers confirms the generic
43 character of elastic properties present at a macroscopic scale in the liquid state (length scales
44 up to 0.500mm have been probed with polymers). The measurement of finite shear elasticity
45 at low frequency indicate very long solid-like correlations and implies for the low molecular
46 weight glass former that the α -process cannot be the slowest relaxation process in the liquid
47 state. Similarly, the reptation time of polymers defined in conventional viscoelasticity by the
48 interception at low frequency of the ω and ω^2 scaling of the elastic and viscous moduli, is not
49 the longest time for the melt state of polymers since the flow regime is replaced at low
50 thickness by an elastic plateau.

51 In the polymer case, the elastic effects are sufficiently strong to provide a solid-like
52 response measurable up to 0.5mm gap thickness and that merges with the high frequency
53 rubbery elasticity at low thickness (0.025mm). The study of several melts ranging from small
54 to high molecular lengths shows that the narrow gap elasticity coincides, via its modulus
55 value ($G' = G_N^0$) to the ordinary rubbery plateau; the elastic and the entanglement forces are
56
57
58
59
60

1
2
3 undistinguishable. The existence of a terminal elasticity in the melt of entangled polymers and
4 of unentangled polymers proves that the notion of entanglements remains vague and that it
5 cannot be considered as a unique origin of the elasticity. This claim is supported by other
6 observations confirming the undefined physical meaning of entanglements[26]. In this frame,
7 a special attention should be paid to theoretical approaches[27] taking into account
8 intermolecular interactions, and not only intrachain statistics (Rouse, reptation). NMR
9 measurements[28] have shown that dominant contributions may be due to interchain forces.
10 More generally, theoretical approaches describing the liquid state [1,29,30] as a condensed
11 matter state predict a finite shear modulus. In this frame, an advanced theoretical development
12 called NEVET [30] is even able to foresee dimensional effects as those observed in the
13 present results. Interestingly, this model explains the supercooled state as an extraordinary
14 expanded crystal-melt phase transition[30].
15
16

17
18 Solid-state properties in liquids have been already reported mainly due to the
19 pioneering Surface Forces Apparatus measurements[31,32,33] and piezorheometry[34].
20 Related to surface induced effects or to intrinsic properties, they reveal scale-dependent
21 interactions at molecular scale or at a multiple of that. At a micron scale, the first claim of
22 identification of non-vanishing shear elasticity interpreted as a condensed matter property is
23 due to Derjaguin using the atomic vibration of a piezomembrane to impose the strain. At
24 higher frequencies (10MHz) and using similar techniques, Bund et al report on also on elastic
25 properties in low and medium viscosity liquids[35]. Later, a gel-like behaviour is reported in
26 untangled polymer melts up to 50 μ m gap thicknesses, but it was interpreted by dynamic
27 heterogeneities (clusters) associated to the glass transition[36]. The present results show that
28 the liquid state of the o-Terphenyl displays a non-negligible and macroscopic *solid-like*
29 character observable at temperatures significantly over the melting point. These observations
30 carried out significantly over the glass transition and the melting point, exclude effect of glass
31 transition clustering[14,36], dusts, of confinement-induced solidification, shear-induced
32 crystallisation near the supercooled state. Very recently, stress-imposed experiments[37] have
33 revealed in the supercooled state a delicate elastic response in the supercooled state of the o-
34 Terphenyl. X-ray photon correlation spectroscopy shows that the analysis of capillary waves
35 of supercooled PPG requires an elastic term in addition to the viscous contribution[8] Other
36 recent developments in dielectric relaxation may indicate a slow relaxation mode so far
37 unidentified[6]. These are converging results; they show that against the common wisdom, the
38 α -relaxation and the reptation time cannot be considered as the terminal relaxation time, i.e.
39 the longest time scale in the sample. The intermolecular interactions and the elastic properties
40 related to these ones contribute to the energy of the condensed matter state. The necessity of
41 applying considerable negative pressures for a solid-vapour transition shows that this energy
42 is not negligible[38]. The finite shear elasticity might be one aspect of this property.
43
44
45
46

47 Acknowledgments:

48 The authors are very grateful to Veeco society for providing high resolution AFM photographs on our alumina
49 substrates.
50
51
52
53
54
55
56
57
58
59
60

Figure captions:

Figure 1a: Dynamic relaxation response in the liquid phase of the o-Terphenyl displayed at 63.7°C ($T_m=56^\circ\text{C}$) and 45 μm (alumina surfaces, plate-plate geometry): - the upper data are measured in the linear regime at 1% strain amplitude (shear modulus G' (\bullet), loss modulus G'' (\blacksquare)), - the low value data are measured at high strain amplitudes (500%: G'' (Δ), 1000%: G'' (\circ)), G' is not represented being below the device resolution). The conventional viscous law ($G'' = \eta \cdot \omega$) symbolised by the blue straight line is fulfilled at large strain amplitude.

Figure 1b: Upper Photograph: AFM picture of a flat zone of the alumina substrate. The grained relief is produced by the alumina crystallites.

Bottom photograph: alumina fixture setup (20mm diameter) – the gap (filled with liquid OTP) is 45 μm .

Figure 1d: Influence of the gap thickness on the shear modulus dynamic response G' (\blacksquare), in the liquid phase of the o-Terphenyl (OTP) displayed at 66°C ($T_m=56^\circ\text{C}$) (alumina surfaces, plate-plate geometry, strain amplitude $\gamma=1\%$). The dotted line is an eye guide.



Figure 1c: Strain dependence (non-linear regime) of the shear modulus G' (red curves) and viscous modulus G'' (blue curves) as a function of the strain amplitude (%) measured in the liquid phase of the OTP ($T=64^\circ\text{C}$). The strain amplitude is indicated on the left extremity of each curve. The dotted line symbolises the ω -scaling dependence. The gap is 25 μm . The right inset points out the opposite strain-induced evolution of the elastic modulus G' (\bullet) and of the viscous modulus G'' (\bullet) at 10rad/s.

Figure 1e: Dynamic response obtained in the supercooled phase of the OTP at 54.6°C ($T = T_m - 1.4^\circ\text{C}$) and 45 μm gap thickness (alumina surfaces, plate-plate geometry). Data measured at 1% strain amplitude (shear modulus G' (\bullet), loss modulus G'' (\blacksquare)) are superposed to those determined at 3% (shear modulus G' (\circ), loss modulus G'' (\circ)). The inset in the figure displays the evolution of the shear modulus as a function of the temperature.

Figure 2b: Solid-like dynamic response observed at low frequency in the melt state of an entangled Polybutylacrylate sample (*PBuA* $M_w=47500$) at 25°C and at 25 μ m.

Figure 2c: Influence of the gap thickness e , on the shear modulus G' of the Polybutylacrylate sample (*PBuA* $M_w=47500$) at 25°C and at 25 μ m. The dotted line is an eye guide.

Table 1:

o-Terphenyl (OTP)	Polybutylacrylate (PBuA)					
 $T_g = -30 \pm 1^\circ\text{C}$, $T_m = 56^\circ\text{C}$	 $M_e = 22000$; $T_g = -64^\circ\text{C}$					
Molecular weight: 230	Molecular weight:	13500	20000	25700	47500	91000
	Polydispersity:	1.10	1.10	1.08	1.08	1.18

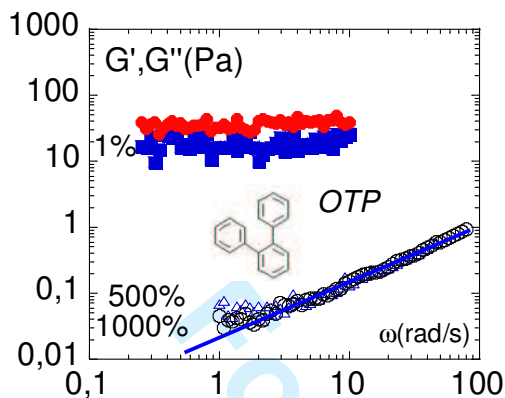


Figure 1a

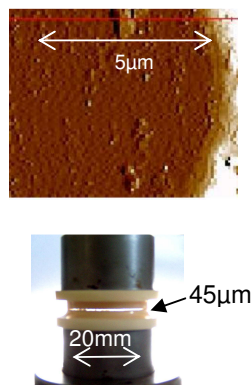


Figure 1b

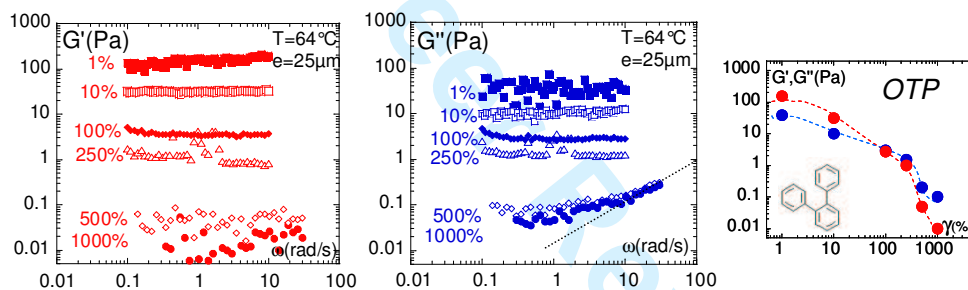


Figure 1c

Influence of the thickness gap

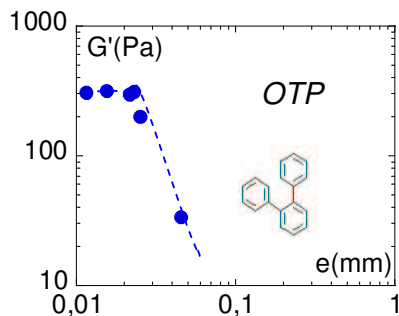


Figure 1d

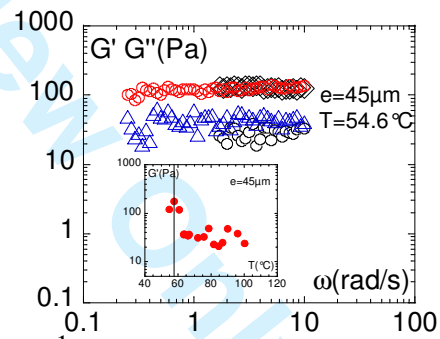


Figure 1e

Influence of the thickness gap

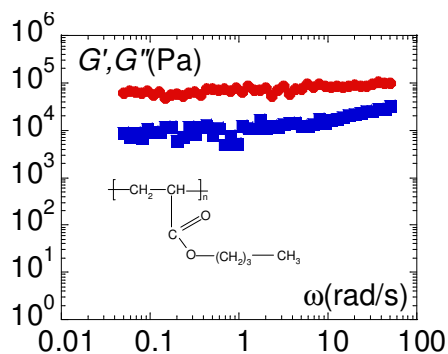


Figure 2a

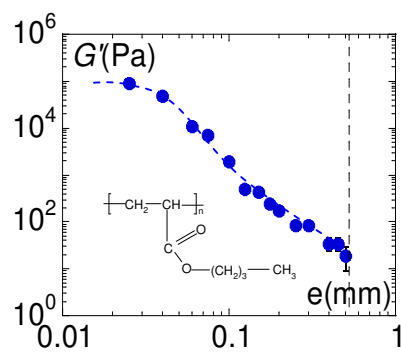


Figure 2b

Influence of the molecular weight

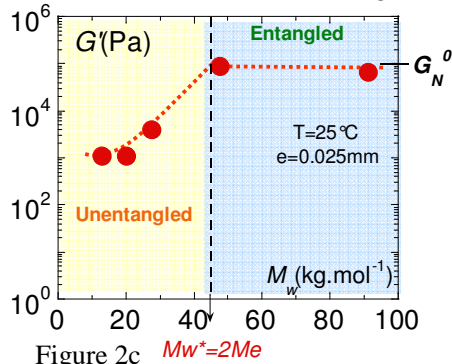


Figure 2c

1
2
3 Short biographical notes:

4 Laurence Noirez is CNRS Research Director.

5 Hakima Mendil-Jakani is CEA senior scientist.

6 Patrick Baroni is CNRS Engineer.

7
8 References:

9
10 [1] Granato A.V., J. de Physique IV, C8 6 (1996) p.1.

11
12 [2] Baroni, P., Mendil, H., Noirez, L., Fr. Pat., 05 10988, (2005), P. Baroni, H. Mendil-Jakani,
13 L. Noirez, *Techniques de l'Ingénieur*, TI Editions, 1 (2010) RE145.

14
15 [3] L. Noirez, P. Baroni, J. of Molecular Structure, 972 (2010) p.16.

16
17 [4] H. Mendil, P. Baroni, L. Noirez, *Eur. Phys. J. E* 2006, 19, p.77.

18
19 [5] J. Goyon, A. Colin, G. Ovarlez, A. Ajdari, L. Bocquet, Nature, 454 (2008) p.84, J. Goyon,
20 A. Colin and L. Bocquet, DOI: 10.1039/c001930e.

21
22 [6] H. Jansson, R. Bergman, J. Swensson, Phys. Rev. Lett. 104 (2010) p.17802.

23
24 [7] U. Tracht, M. Wilhelm, A. Heuer, H. Feng, K. Schmidt-Rohr, H.W. Spiess, Phys. Rev.
25 Lett. 81 (1998) p.2727.

26
27 [8] Y. Chushkin, C. Caronna, A. Madsen, A., EPL, 2008, 83, p.36001.

28
29 [9] E.C. Fuchs, P. Baroni, B. Bitschnau, L. Noirez, J. of Physics D, 43 (2010) p.105502.

30
31 [10] S.S. Chang, A.B. Bestul, J. Chem. Phys. 56 (1972) p.503.

32
33 [11] I. Lugoski, Karle, L.O. Brockway, JACS, 66 (1944) p.1974.

34
35 [12] M.D. Ediger, C.A. Angell, S. R. Nagel, J. Phys. Chem. 100 (1996) p.13200.

36
37 [13] G.P. Johari M. Goldstein, J. Chem. Phys. 53 (1970) p.2373.

38
39 [14] W. Steffens, A. Patkowski, G. Meier, E.W. Fischer, J. Chem. Phys. 96 (1992) 4171,
40 E.W. Fischer, Physica A 201 (1993) p.183.

41
42 [15] F. Fujara, B. Geil, H. Sillescu, G. Fleischer, Z. Phys. B 88 (1992) p.195.

43
44 [16] W. Petry, E. Bartsch, F. Fujara, M. Kiebel, H. Sillescu, B. Farago, Z. Phys. B 83 (1991)
45 p.175.

46
47 [17] T. Young, *An essay of the cohesion of fluids*, Philos. Trans. Soc., London, 95 (1805)
48 p.65; P.G. de Gennes, F. Brochard-Wyart, D. Quéré, "*Gouttes, bulles, perles et ondes*", Belin
49 Ed. 2005.

50
51 [18] D. Tolstoï, Molecular Theory for slippage of liquids over solid surface, Doklady Akad.
52 Nauk. SSSR 85 (1952) p.1089.

- 1
2
3 [19] W. H. Hedley, M. V. Milnes, W. H. Yanko, *J. Chem. Eng. Data*, 15 (1) (1970) p.122.
4
5 [20] H. Lakrout, C. Creton, D. Ahn, K.R. Shull, *Macromol.* 34 (2001) p.7448.
6
7 [21] J.D. Ferry, *Viscoelastic properties of polymers*, Wiley 1971; W. Graessley, *Adv. Poly.*
8 *Sci.* 16 (1974) p.1; Graessley, *Polymer* 21 (1980) p.258.
9
10 [22] J. Rault, *J. Non-Newtonian Fluid Mechanics* 23 (1987) p.229.
11
12 [23] M.D. Ediger, C.A., Angell, Nagle S.R., *J. Phys. Chem.* 100 (1996) p.13200.
13
14 [24] Z.P. Bazant, *Scaling of Structural Strengths*, Hermes Penton Science, London, 2002.
15
16 [25] J.P. Heller and M.S. Kuntamukkula, *Ind. Eng. Chem. Res.* 26 (1986) .318.
17
18 [26] J.A. Martins, *Macromol. Theory Simul.* 19 (2010) p.360.
19
20 [27] J.P. Ibar, *J.M.S. –Rev. Macromol. Chem. Phys.*, C37 (1997) p.389.
21
22 [28] P. Sotta, B. Deloche, J. Herz, A. Lapp, D. Durand, J.-C. Rabadeux, *Macromol.*, 20
23 (1987) p.2769.
24
25 [29] A.V. Granato., *Materials Science and Engineering A* 521 (2009) p.6.
26
27 [30] F. Volino, *Annales de Physique*, 22 n°1 & 2 Chapter VI (1997).
28
29 [31] Hu H.-W.,Carson, Granick S. *Phys.Rev.Lett.*, 1991, 66, 2758; Zhu Y., Granick S. *Phys.*
30 *Rev. Lett.*, 93 (2004) p.0961011; J.N. Israelachvili, P.M. Mcguiggan, A.M. Homola, *Science*
31 240 (1988) p.189.
32
33 [32] J.N. Israelachvili, R. Pashley, *Nature* 300 (1982) p.341.
34
35 [33] A. Maali., T. Cohen-Bouhacina, G. Couturier, J.P. Aimé, *Phys. Rev. Lett.*, 96 (2006)
36 p.861051.
37
38 [34] B.B. Badmaev., U.B. Bazarov, B.V. Derjaguin, O.R. Budaev, *Physica B* 122 (1983)
39 p.241, B.V. Derjaguin, U.B. Bazarov, K.T. Zandanova, O.R. Budaev *Polymer*, 30 (1989)
40 p.97.
41
42 [35] A. Bund, G. Schwitzgebel, *Anal. Chem.* 70 (1998) p.2584.
43
44 [36] D. Collin, P. Martinoty, *Physica A*, 320 (2002) p.235.
45
46 [37] R. Zondervan, T. Xia, H. van der Meer, C. Sorm, F. Kulzer, W. van Saarloos, M. Orrit.
47 *PNAS*, 105 (2008) p.4993.
48
49 [38] A.R. Imre, *Phys. Stat. Sol.* 244 (2007) p.893.
50
51
52
53
54
55
56
57
58
59
60