



HAL
open science

Comment on "Electronic Structure of Superconducting KC8 and Nonsuperconducting LiC6 Graphite Intercalation Compounds: Evidence for a Graphene-Sheet-Driven Superconducting State"

Matteo Calandra, Claudio Attaccalite, Giovanni Profeta, Francesco Mauri

► **To cite this version:**

Matteo Calandra, Claudio Attaccalite, Giovanni Profeta, Francesco Mauri. Comment on "Electronic Structure of Superconducting KC8 and Nonsuperconducting LiC6 Graphite Intercalation Compounds: Evidence for a Graphene-Sheet-Driven Superconducting State". *Physical Review Letters*, 2012, 108, pp.149701. 10.1103/PhysRevLett.108.149701 . hal-00692115

HAL Id: hal-00692115

<https://hal.science/hal-00692115>

Submitted on 28 Apr 2012

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Comment on "Electronic Structure of Superconducting KC_8 and Nonsuperconducting LiC_6 Graphite Intercalation Compounds: Evidence for a Graphene-Sheet-Driven Superconducting State from electron-phonon interaction."

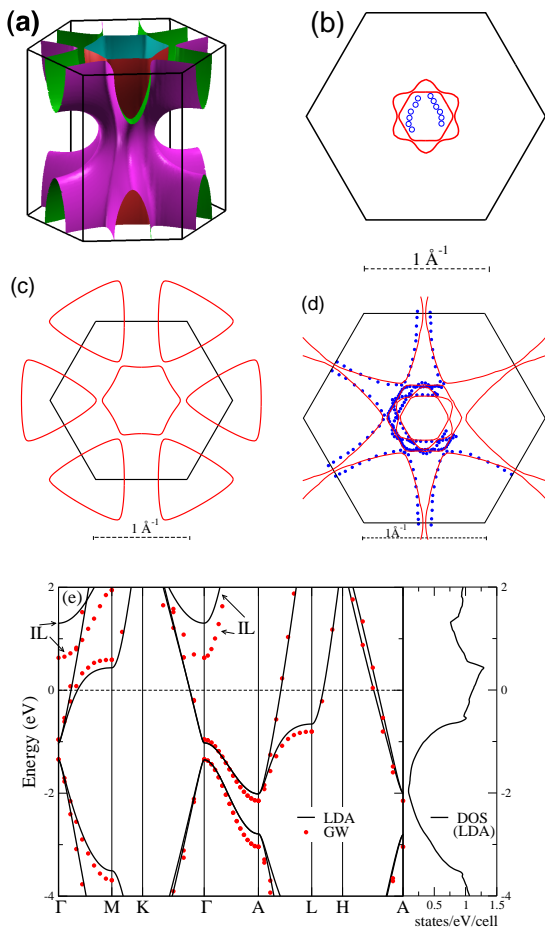


FIG. 1. (color online):(a) DFT Fermi surface of Bulk LiC_6 (Li stacking is AA) [2] and cuts over the $k_z = 0$ (b) and $k_z = \pi/c$ (c) planes within the local density approximation (LDA). In (b) empty blue dots are ARPES data from [1]. (d) DFT Fermi surface (red) of a Li-intercalated graphene bilayer (C_6LiC_6) compared with ARPES data (blue dots) from ref. [3]. (e) DFT and GW bulk LiC_6 electronic-structure. The Fermi level is at zero. IL labels the metal-interlayer state. In all plots we use the LiC_6 Brillouin zone where the graphene Dirac point is folded at Γ .

In [1] it is claimed that the charge transfer from the

metal to the graphene layers is larger in KC_8 than in LiC_6 . This relies on a two-dimensional analysis of photoemission (ARPES) data that, *a priori* and without experimental verification, totally neglects the electronic band dispersion perpendicular to the graphene planes. Pan *et al.* could have verified this assumption by performing ARPES measurements as a function of the photon energy, as it was done for the out-of-plane dispersion in graphite [4]. Here we demonstrate that, in LiC_6 , the small interlayer distance results in a very high band-dispersion along the k_z direction, invalidating the analysis and the conclusions of [1].

The density-functional-theory (DFT) band-structure in Fig. 1 (e) is highly dispersive along k_z (ΓA direction) by more than 1.2 eV. This results in the three-dimensional Fermi surface shown in Fig. 1 (a),(b) and (c). Note, in particular, that the Fermi surface cuts in the $k_z = 0$ and $k_z = \pi/c$ planes are completely different, the $k_z = 0$ being closer to the experimental data in [1].

Correlation effects slightly increase the k_z dispersion in bulk LiC_6 as shown by our GW [5] calculation. Both GW and DFT find an empty interlayer metal state in LiC_6 [6, 7] (complete charge-transfer from Li to graphene) and a partially occupied one in KC_8 (incomplete charge-transfer from K) [7, 8]. Thus the calculated charge-transfer is larger in LiC_6 than in KC_8 , in disagreement with Ref. [1].

To validate the accuracy of DFT on Li intercalated graphite systems, we calculate[9] the Fermi surface of a Li-intercalated graphene bilayer, obtaining results in excellent agreement with ARPES data [3] (Fig. 1 (d)). The experimental Fermi surface splitting of the bilayer measures the hopping between graphene planes separated by Li atoms and, indirectly, the k_z dispersion in the bulk. Indeed, the hopping between graphene planes is a properties of the local geometry which is identical in bulk LiC_6 and in the C_6LiC_6 bilayer.

In conclusion, the three dimensional character of the Fermi surface of bulk LiC_6 , neglected in the analysis of [1], invalidates the charge-transfer estimate of [1] and the subsequent claim of a graphene-sheet-driven superconducting state.

M. Calandra,¹ C. Attaccalite,³ G. Profeta² and F. Mauri¹
¹ IMPMC, Université Paris 6, CNRS, 4 Place Jussieu, 7504 Paris, France

²Institut Neel, CNRS/UJF, 25 rue des Martyrs BP 166, Batiment D, F-38042 Grenoble cedex 9, France

³ SPIN-CNR - Dip. di Fisica Università degli Studi di L'Aquila, 67100 L'Aquila, Italy

[1] Z.-H. Pan *et al.*, Phys. Rev. Lett. **106**, 187002 (2011)
 [2] D. Guerd and A. Herold, Carbon, **13**, 337 (1975)
 [3] K. Sugawara, *et al.*, AIP Advances **1**, 022103 (2011)
 [4] A. Grüneis *et al.* Phys. Rev. Lett. **100**, 037601 (2008)
 [5] A. Marini, C. Hogan, M. Grüning, D. Varsano, Comp.

Phys. Comm. **180**, 1392 (2009).
 [6] N. A. W. Holzwarth, S. G. Louie, S. R. Rabii, Phys. Rev. B **28**,1013 (1983)
 [7] G. Csanyi *et al.*, Nature Physics **1**, 42 (2005)
 [8] A. Grüneis, *et al.* Phys. Rev. B **79**, 205106 (2009)

- [9] P. Giannozzi *et al.*, J. Phys. Cond. Matt. **21**, 395502 (2009), <http://www.quantum-espresso.org>