



HAL
open science

Theoretical analysis of fiber lasers emitting around 810 nm based on thulium-doped silica fibers with enhanced 3H4 level lifetime

Pavel Peterka, Ivan Kasik, Bernard Dussardier, Wilfried Blanc

► To cite this version:

Pavel Peterka, Ivan Kasik, Bernard Dussardier, Wilfried Blanc. Theoretical analysis of fiber lasers emitting around 810 nm based on thulium-doped silica fibers with enhanced 3H4 level lifetime. 4th EPS-QEOD Europhoton Conference, Aug 2010, Hamburg, Germany. pp.WeP5. <hal-00732350>

HAL Id: hal-00732350

<https://hal.science/hal-00732350v1>

Submitted on 14 Sep 2012

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



HAL Authorization

Theoretical analysis of fiber lasers emitting around 810 nm based on thulium-doped silica fibers with enhanced $^3\text{H}_4$ level lifetime

P. Peterka¹, I. Kasik¹, B. Dussardier², W. Blanc²

¹ Institute of Photonics and Electronics Academy of Science of the Czech Republic, v.v.i., 18251 Prague, Czech Republic,

² Laboratoire de Physique de la Matière Condensée, Université de Nice-Sophia-Antipolis, CNRS UMR 6622, Avenue Joseph Vallot, Parc Valrose, 06108 NICE CEDEX 2, France

Most exploited operating wavelengths offered by rare-earth doped fiber lasers are situated around 1, 1.5 and 2 μm . In this paper we investigate thulium-doped fiber (TDF) laser operating around 800 nm that would extend the spectral range already covered by high-power fiber lasers. The single-transverse mode, high-power laser source in the 800 nm spectral band can be used for fiber sensors, instrument testing and for pumping of special types of lasers and amplifiers. Particularly, bismuth-doped fibers pumped around 800 nm may shift their gain to 1300 nm telecommunication band, where highly reliable silica-based fiber amplifiers are still unavailable. The proposed laser has a compact all-fiber setup (see Fig. 1) with upconversion pumping scheme according to Fig. 2a. Amplification and lasing at 800 nm band has already been investigated using low-phonon energy fluoride-based TDFs. Output power of up to 2 W and 37% slope efficiency was achieved [1]. However, usage of fluoride fibers results in difficulties with fabrication, hygroscopicity and aging of the host material and low pump power damage threshold as observed in [1].

Using a comprehensive numerical model of TDF we investigate performance of the proposed laser at around 810 nm in three different hosts: fluoride glass (ZBLAN), standard silica and silica modified by high alumina codoping. This last fiber composition is of interest because we have shown that with modification of local environment of the thulium ions by alumina, the fluorescence lifetime of the $^3\text{H}_4$ level is significantly increased [2, 3]. The spectroscopic parameters of the modified silica fiber used in the modelling are summarized in [4]. The main difference between the three hosts relevant to the proposed application is the $^3\text{H}_4$ fluorescence lifetime of the three different materials as noted in Fig. 2b. Because the laser characteristics of the laser output power vs. input pump power is not strictly linear due to possible population of the $^1\text{G}_4$ level, we do not compare performance of the three host materials in terms of slope efficiency and threshold. Instead, they are compared simply in terms of the output power. It can be seen in Fig. 2b that lasing at 810 nm is hardly to achieve with silica based Tm-doped fiber in contrast to the fluoride host materials. However, the lasing might be possible even for silica based fiber for specific short ranges of the fiber and laser cavity parameters, especially when $^3\text{H}_4$ lifetime is enhanced. The laser tunability and effect of photodarkening will be also discussed in the presentation.

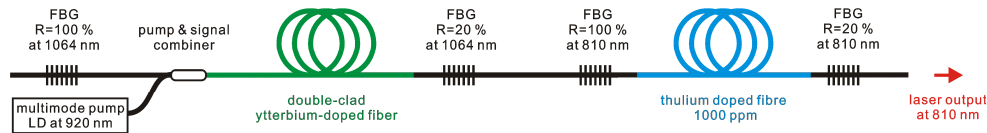


Fig. 1 Fiber laser setup in compact all-fiber arrangement.

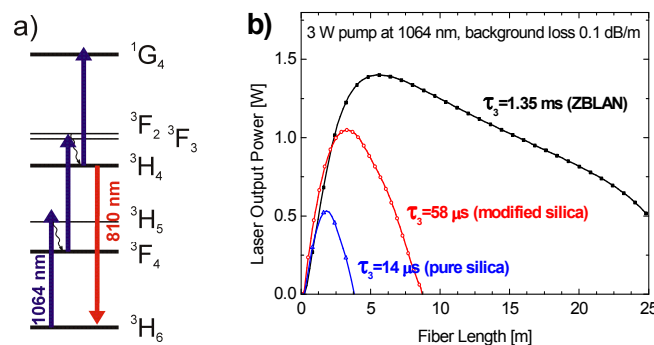


Fig. 2 Single wavelength upconversion pumping scheme (a), effect of host material (b). The optimized waveguide parameters were used: the core diameter of 3.4 μm and numerical aperture of 0.2.

References

- [1] M. L. Dennis, J. W. Dixon and I. Aggarwal, "High power upconversion lasing at 810 nm in Tm:ZBLAN fibre", *El. Lett.* **30**:136 (1994).
- [2] W. Blanc, T. L. Sebastian, B. Dussardier, C. Michel, B. Faure, M. Ude and G. Monnom, "Thulium environment in a silica doped optical fibre", *J. Non-Cryst. Solids*, **354**:435 (2008).
- [3] B. Faure, W. Blanc, B. Dussardier and G. Monnom, "Improvement of the Tm³⁺: $^3\text{H}_4$ level lifetime in silica optical fibers by lowering the local phonon energy", *J. Non-Cryst. Solids*, **353**:2767 (2007).
- [4] P. Peterka, I. Kasik, V. Matejec, W. Blanc, B. Faure, B. Dussardier, G. Monnom and V. Kubecek, "Thulium-doped silica-based optical fibers for cladding-pumped fiber amplifiers", *Optical Materials* **30**:174 (2007).