



HAL
open science

Modelling of colour change induced by aging and heat treatment by using the multi-process kinetic analysis

Miyuki Matsuo, Joseph Gril, Misao Yokoyama, Kenji Umemura, Shuichi Kawai

► **To cite this version:**

Miyuki Matsuo, Joseph Gril, Misao Yokoyama, Kenji Umemura, Shuichi Kawai. Modelling of colour change induced by aging and heat treatment by using the multi-process kinetic analysis. 1st Workshop of COST Action FP0904 'Mechano-Chemical transformations of wood during Thermo-Hydro-Mechanical processing', Feb 2011, Bienne, Switzerland. <hal-00796689>

HAL Id: hal-00796689

<https://hal.science/hal-00796689v1>

Submitted on 4 Mar 2013

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



HAL Authorization

Modelling of colour change induced by aging and heat treatment by using the multi-process kinetic analysis

Miyuki Matsuo^{*1}, Joseph Gril², Misao Yokoyama¹, Kenji Umemura¹, Shuichi Kawai¹

¹Research Institute for Sustainable Humanosphere, Kyoto University, Gokasho, Uji, Kyoto, Japan.
 *matsuomiyuki@rish.kyoto-u.ac.jp

²Laboratoire de Mécanique et Génie Civil, Université Montpellier 2, CNRS, CC 048 Place
 Eugène Bataillon, 34095 Montpellier Cedex 5, France
 joseph.gril@univ-montp2.fr

Key words: colour change, accelerated aging, natural aging, kinetic analysis, historical buildings

Abstract

Colour of wood changes both during natural aging and during heat treatment. Colour measuring, which is non-destructive and requires only a small area, might be an useful tool as an aging or deterioration index. Exact modelling of colour changes is important not only to predict deterioration but also to understand the aging and deterioration mechanism of wood. This study deals with the modelling of colour changes that occur both during natural aging and during heat treatment by using kinetic analysis. For better understanding of the process of colour change, we employed multi-process kinetic analysis.

Hinoki (*Chamaecyparis obtusa* Endl.), which is a typical species used for historical buildings and Buddhist sculptures in Japan, was used. Naturally aged wood specimens were prepared from the members of historical buildings built in from 7th century to 15th century. Namely, the aging time ranged from approximately 550 years to 1600 years [1][3]. The specimens for heat treatment were prepared from the wood harvested in 1988. Completely-dried specimens were treated at 90°C, 120°C, 150°C, and 180 °C. The treatment duration ranged from 0.5 hours to approximately 2 years [2]. The colour of the specimens was measured with a spectrophotometer (KONICA MINOLTA CM-2600d) and was expressed by CIELAB colour parameters (L^* , a^* , and b^*). Figure 1 shows the examples of the colour change during natural aging and heat treatment.

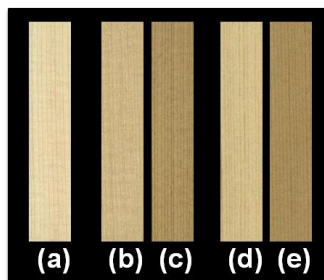


Figure 1: Colour change of hinoki wood during natural aging and during heat treatment. (a) wood harvested in 1998 as a control, (b) aged in the ambient condition for 750 years; (c) for 1600 years, (d) treated at 180°C for 2 hours; (e) for 12 hours.

When modelling colour changes induced by natural aging and heat treatment, we assumed that the change of a colour parameter x can be decomposed as

$$x = x_0 + x_1 + \dots + x_N \quad (1)$$

COST Action FP0904 „Thermo-Hydro-Mechanical Wood Behaviour and Processing“
 February 16-18, 2011 / Biel (Bienne), Switzerland

where x_0 represents the initial colour value before natural aging or heat treatment, x_k ($k > 0$) are variation of x related to independent chemical or physical processes. Each x_k starts from 0 in the initial state and approaches a limiting value X_k following a first-order kinetic;

$$x_k(t) = X_k[1 - \exp(-t/a_T)] \quad (k = 1 \dots N) \quad (2)$$

where t is aging or treatment time and a_T is a time-temperature dependent shift factor at the aging or treatment temperature T . We chose $N = 3$ on a trial basis because the trend of colour changes indicated that at least 3 processes of the reactions occurred; i.e. the change of a colour parameter x can be expressed as follows:

$$x(t) = X_1[1 - \exp(-t/a_T)] + X_2[1 - \exp(-t/a_T)] + X_3[1 - \exp(-t/a_T)] \quad (3)$$

The apparent activation energies for each process were calculated.

The models calculated well fitted with the measured colour changes in all colour parameters, L^* , a^* , and b^* . The modelled and measured value of L^* is shown in Fig. 3 as an example. The calculated activation energies for the first, second, and third process were 130, 109, and 135 kJ/mol, respectively. The successful modelling and the calculated kinetic parameters will bring important information about the behaviour of colour during aging and heat treatment.

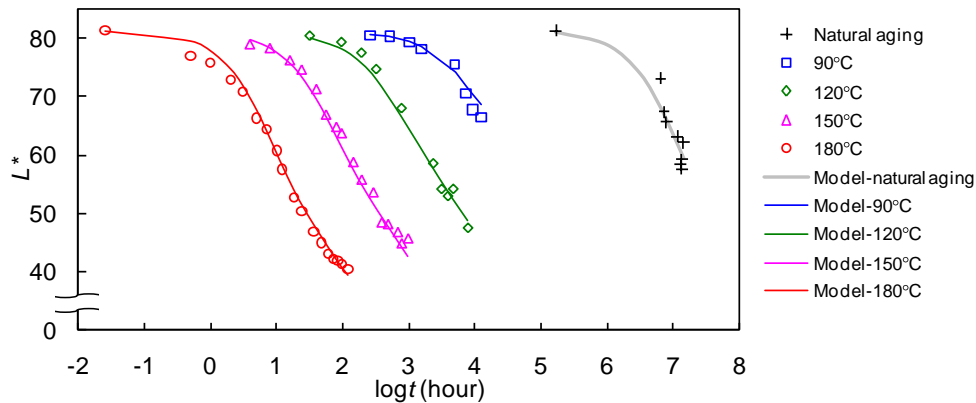


Figure 2: Measured colour value L^* of natural aging wood and heat treated wood and the models produced by kinetic analysis considering 3 first-order processes.

Acknowledgement: This work was supported by a Grant-in-Aid for Scientific Research (A) (No. 20248020) and for JSPS Fellows (No. 21-2994) from the Japan Society for the Promotion of Science. A part of this work was presented in Wood CulTher COST IE0601 Symposium in Braga (2008) and in Hamburg (2009).

References

- [1] Yokoyama, M., Gril, J., Matsuo, M., Yano, H., Sugiyama, J., Clair, B., Kubodera, S., Mitsutani, T., Sakamoto, M., Ozaki, H., Imamura, M., Kawai, S. (2009) Mechanical characteristics of aged hinoki wood from Japanese historical buildings, *C. R. Phys.* 10(7):601-11.
- [2] Matsuo, M., Yokoyama, M., Umemura, K., Gril, J., Yano, K., Kawai, S., (2010), Color changes in wood during heating: Kinetic analysis by applying a time-temperature superposition method, *Appl. Phys. A* 99(1):1-6.
- [3] Matsuo, M., Yokoyama, M., Umemura, K., Sugiyama, J., Kawai, S., Gril, J., Kubodera, S., Mitsutani, T., Ozaki, H., Sakamoto, M., Imamura, M., Aging of wood - Analysis of color changes during natural aging and heat treatment -, *submitted to Holzforschung*