



**HAL**  
open science

## Synchronized B and <sup>13</sup>C Diamond Delta Structures for an Ultimate In-Depth Chemical Characterization

Alexandre Fiori, François Jomard, Tokuyuki Teraji, Satoshi Koizumi, Junichi Isoya, Etienne Gheeraert, Etienne Bustarret

► **To cite this version:**

Alexandre Fiori, François Jomard, Tokuyuki Teraji, Satoshi Koizumi, Junichi Isoya, et al.. Synchronized B and <sup>13</sup>C Diamond Delta Structures for an Ultimate In-Depth Chemical Characterization. Japanese Journal of Applied Physics, part 2 : Letters, 2013, 6, pp.045801. 10.7567/APEX.6.045801 . hal-00838943

**HAL Id: hal-00838943**

**<https://hal.science/hal-00838943>**

Submitted on 26 Jun 2013

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

## Title

Synchronized B and  $^{13}\text{C}$  Diamond Delta Structures for an Ultimate In-Depth Chemical Characterization

## Authors

Alexandre Fiori<sup>\*1,2</sup>, François Jomard<sup>3</sup>, Tokuyuki Teraji<sup>2</sup>, Satoshi Koizumi<sup>2</sup>, Junichi Isoya<sup>4</sup>, Etienne Gheeraert<sup>1</sup>, and Etienne Bustarret<sup>1</sup>

## Affiliations

<sup>1</sup>Institut Néel, CNRS and Université Joseph Fourier, BP 166, 38042 Grenoble Cedex 9, France

<sup>2</sup>National Institute for Materials Science, 1-1 Namiki, Tsukuba, Ibaraki, 305-0044, Japan

<sup>3</sup>GEMaC, CNRS and Université Versailles St Quentin, 45, avenue des Etats-Unis, 78035 Versailles Cedex, France

<sup>4</sup>Tsukuba University, 1-2 Kasuga, Tsukuba, Ibaraki 305-8550, Japan

\*E-mail address: FIORI.Alexandre@nims.go.jp

## Abstract

The nanometer-range depth resolution of secondary ion mass spectrometry (SIMS) profiles in diamond was achieved by the determination of the depth resolution function (DRF). The measurement of this DRF was performed thanks to isotopic-enriched diamond delta structures composed of  $^{12}\text{C}$  and  $^{13}\text{C}$ . The artificial SIMS broadening observed on the  $^{13}\text{C}$  depth profiles of buried doped diamond epilayers was eliminated and replaced by a boxlike  $^{13}\text{C}$  depth profile. Applied to boron delta-doped diamond structures, this analysis has resolved edge widths close to 0.3 nm/dec, as compared with 1.5 nm/decade on the raw SIMS data.

1 Diamond has several excellent characteristics, superior to those of other semiconductors, e.g., Si  
2 and SiC. The high breakdown voltage and high temperature operation of diamond have strongly  
3 motivated research aiming at the development of next-generation high-power devices.<sup>1)</sup> More in line  
4 with the optical properties that have given diamond its value as a jewel, modern diamond research is  
5 also focused on photonics and spintronics related to colour centers, e.g., NV centers in diamond.<sup>2-3)</sup>  
6 Both types of application require the availability of very thin doped layers (boron or nitrogen-doped) in  
7 the range of nanometer thickness, the so-called “delta structures”,<sup>3-5)</sup> as well as the possibility to  
8 characterize such ultrathin epilayers.

9 Secondary ion mass spectrometry (SIMS) is commonly used to obtain depth profiles of dopant  
10 concentrations in diamond and other semiconductors. This technique uses a bombardment by energetic  
11 ions (usually  $\text{Cs}^+$  or  $\text{O}_2^+$ ) to sputter and simultaneously mass-select recoiled secondary ions. The depth  
12 resolution of the depth concentration profile is mainly limited by primary ion masses, by incident and  
13 detected ion kinetic energies, by the incidence and collection angles, and by the roughness of the  
14 sample. Indeed, a SIMS-induced ion mixing is particularly visible when two adjacent layers, in the  
15 same sample, have a large and abrupt difference in doping level or in chemical composition. Below 100  
16 nm in thickness, this effect is no longer negligible; it strongly affects the depth profile measurements  
17 by broadening, so that the raw SIMS profile ( $P_{\text{SIMS}}$ ) differs from the dopant profile ( $P_{\text{Dopant}}$ ), up to the  
18 point where the thickness values and atom peak concentrations in multilayer stacks become erroneous.

19 Technically, during a SIMS analysis, the experimental depth profile ( $P_{\text{SIMS}}$ ) is the convolution of  
20 the dopant depth profile ( $P_{\text{Dopant}}$ ) and of the depth resolution function (DRF).<sup>6)</sup> Evaluation of this DRF  
21 (which depends on the probed atom) is a key issue in nanometer-range secondary ion mass  
22 spectrometry and a crucial step toward the prediction of artefacts affecting measured SIMS depth  
23 profiles. Deconvolution analysis using such a DRF provides accurate measurements on steep dopant  
24 depth profiles over many orders of magnitude in concentration. In the context of delta doping, the large  
25 dynamical doping range is a key advantage of SIMS when compared with other nanometric chemical

1 profiling methods such as elastic recoil detection (ERD)<sup>7)</sup>, atom probe tomography<sup>8)</sup> or transmission  
2 electron microscopy-related techniques,<sup>9, 10)</sup> or to more “indirect” probes such as magneto-transport  
3 measurements.<sup>11)</sup>

4 Previous SIMS data processing schemes, especially in the case of diamond boron doping, have  
5 been based on 4-points smoothing techniques,<sup>4)</sup> but do not deal with ion mixing directly, although this  
6 physical process is known to be responsible of the specific exponential shape of the trailing edges in  
7 impurity profiles where a sharp drop of the impurity concentration with depth is expected. To estimate  
8 quantitatively the influence of ion mixing occurring in the diamond during the SIMS analysis (for a  
9 given crystalline orientation and surface roughness), local isotopic substitution (or “isotopically pure  
10 growth”) must be employed, similar to the case of silicon ( $^{28}\text{Si}/^{30}\text{Si}$ ).<sup>12)</sup> Isotope substitution is the ideal  
11 control experiment to extract the best DRF fit, because it introduces only a negligible difference in  
12 mass (same recoiling effect) and no additional crystalline strain (same lattice parameter). In diamond,  
13 carbon is found with two stable isotopes:  $^{12}\text{C}$  and  $^{13}\text{C}$ , and isotopically modulated epitaxial multilayers  
14 have been grown.<sup>13)</sup> Once the DRF expression is known for carbon in diamond, from an isotopic delta-  
15 substituted structure, we can apply this function to determine the deconvoluted dopant depth profile for  
16 both nitrogen and boron, with a negligible error, because of the small difference in mass among boron,  
17 carbon, and nitrogen. Putting aside the influence of ionization ratios, this is similar to the case of  
18 phosphorus in silicon, while the situation of boron-doped silicon would resemble that of phosphorous-  
19 doped diamond, where the depth profiles can be deconvoluted using the DRF of carbon with a possible  
20 correction factor taking into account the effects induced by the mass difference<sup>14)</sup> and ionization ratio  
21 difference.

22 However, recording an accurate DRF is difficult since it requires an extremely thin substituted  
23 layer in order to reproduce a delta function (ideally one monolayer containing a change in the atomic  
24 composition). The fabrication of such a delta structure containing an ultrathin substitutional embedded

1 layer requires strict conditions such as a flat surface, no chemical diffusion in the matter, and a  
2 crystalline substrate.<sup>14)</sup> Diamond epitaxial multilayer stacks fulfill these requirements.

3 According to experiments in silicon,<sup>15)</sup> the SIMS depth profile corresponding to an isotopic delta-  
4 doped layer is not a sharp rectangular-shaped profile, but an arrangement of a Gaussian-like rounded  
5 top with exponentials rising and trailing edges. In this study, we use an analytical expression of the  
6 DRF proposed by Dowsett et al.,<sup>14)</sup> which results in the convolution of a double exponential, governed  
7 by  $\lambda_{\text{up}}$  and  $\lambda_{\text{down}}$  parameters, with a Gaussian function, where  $\sigma$  is related to the full width at half  
8 maximum, as follows:

$$9 \text{ DRF}(z) = \frac{1}{2(\lambda_{\text{up}} + \lambda_{\text{down}})} \times \left\{ \exp\left(\frac{z-z_0}{\lambda_{\text{up}}} + \frac{\sigma^2}{2\lambda_{\text{up}}^2}\right) \times \left[1 + \frac{1}{\sqrt{2}} \cdot \text{erf}\left(\frac{-(z-z_0)}{\sigma} - \frac{\sigma}{\lambda_{\text{up}}}\right)\right] + \exp\left(\frac{-(z-z_0)}{\lambda_{\text{down}}} + \frac{\sigma^2}{2\lambda_{\text{down}}^2}\right) \times \left[1 + \frac{1}{\sqrt{2}} \cdot \text{erf}\left(\frac{z-z_0}{\sigma} - \frac{\sigma}{\lambda_{\text{down}}}\right)\right] \right\}, (1).$$

11 A fourth parameter  $z_0$  represents the position of the cusp of the double exponential.

12 Mathematically, the DRF can be plotted as a depth profile after being convoluted with a Dirac  
13 delta function localized at  $z_0$ , which has no thickness and a maximal top value [see Fig. 1(a)]. SIMS  
14 analysis is usually performed from the sample surface to the substrate, and the ion mixing (forward  
15 scattering of atoms) is then effective from the left to the right on the plot, explaining the profile  
16 asymmetry visible in the Figs. 1–3 as well as in our previous measurements.<sup>5)</sup> Consequently, the “rising”  
17 interface (located above the delta layer) will always show a sharper edge on the original SIMS profile  
18 compared with the broad “falling” tail located below the layer ( $\lambda_{\text{up}} < \lambda_{\text{down}}$ ).

19 A delta-doped layer has a finite thickness, in contrast to the Dirac delta function, which is a  
20 mathematical object. As shown in Fig. 1(b), the convolution of the DRF by a boxlike rectangular signal,  
21 featuring a constant atomic concentration and a finite thickness, is expected to describe a real and  
22 material delta-doping, and differs in its depth profile from the Dirac delta-function response. The SIMS  
23 response to a thin layer with sharp interfaces will appear wider, with smoother interfaces and a lower  
24 peak concentration.

1 Isotope-enriched methane ( $^{12}\text{C}$ : 99.99% +  $^{13}\text{C}$ : 100 ppm) was used to grow the buffer and the cap  
2 diamond layers, while standard methane ( $^{12}\text{C}$ : 98.9 % +  $^{13}\text{C}$ : 1.1%) was used to grow the delta layer in  
3 diamond. In order to minimize surface roughness effects, a particularly flat sample was selected. The  
4 surface was ultra-polished in Japan by Syntek Co., Ltd.; the resulting surface RMS roughness, checked  
5 using a 3D optical profiler, was below 0.3 nm before overgrowth. In this study, 0.5  $\mu\text{m}$  of intrinsic  
6 buffer diamond was grown at the National Institute for Materials Sciences, NIMS (Tsukuba, Japan) in a  
7 high-plasma-density NIMS-type reactor with the  $^{12}\text{C}$ -enriched methane <sup>16)</sup> in order to maintain a good  
8 crystalline quality and a flat surface. Then, a heavy boron-doped layer was grown at Institut Néel  
9 (Grenoble, France) in a modified NIRIM-type reactor designed for delta-doping diamond growth, from  
10 normal  $\text{CH}_4$  abundance ( $^{12}\text{C}$ : 98.9 %) with 0.5% ( $\text{CH}_4/\text{H}_2$ ) and 6000 ppm ( $\text{B}/\text{C}$ )<sub>gas</sub> for 3 mins.<sup>11)</sup> Please  
11 note that in the gas phase, the concentration of  $^{13}\text{C}$  was only about twice that of boron. Finally, the top  
12 layer, i.e., cap layer, was grown at NIMS with isotopic-enriched methane to overgrow 50 nm of  
13 intrinsic diamond. The surface RMS roughness was close to 1 nm after the growth of the whole stack.  
14 No particular etching-back process including either oxygen or hydrogen was applied.<sup>5)</sup> Thus, we report  
15 on a delta layer structure composed of isotopic carbon ( $^{13}\text{C}$ ) and boron.

16 The synchronized boron and isotopic carbon diamond delta structure has been analyzed with a  
17 Cameca IMS 4f apparatus with 14.5 keV  $\text{Cs}^+$  primary ions in GEMaC, by collecting the negative  
18 secondary ions.  $^{13}\text{C}$  and  $^{11}\text{B}$  depth profiles exhibit a similar behavior (Figs. 2 and 3), the boron  
19 incorporation following that of  $^{13}\text{C}$  from methane, as expected. This observation illustrates the  
20 similarity in the fast kinetics of carbon and boron incorporation during growth.

21 The SIMS depth profile of  $^{13}\text{C}$  intensity was fitted first (see Fig. 2) by the convolution of the  
22 depth resolution analytical function, eq. (1), and self-consistently with a rectangular function, already  
23 described in Fig. 1(b). The set of parameters used to create the DRF is shown in Table I, where  $\delta$   
24 represents the substituted structure thickness, i.e., the width of the rectangular function.

1           These values were in good agreement with physical parameters. Indeed, the ion mixing simulated  
2 by ion recoil of carbon atoms induced by the  $\text{Cs}^+$  primary ion beam in a Monte Carlo method  
3 algorithm<sup>17)</sup> was in the 3 nm range. This value was similar to the broad trailing edge ( $\lambda_{\text{down}}$ ). In addition,  
4 the rising exponential component ( $\lambda_{\text{up}}$ ) of the DRF, which was around 1 nm, was compatible with the  
5 observed backscattering. The 50 nm thickness of the cap layer agreed with the position of the cusp ( $z_0$ )  
6 in the double-exponential component of the DRF. The thickness of the delta layer measured using  $^{13}\text{C}$   
7 was compatible with the growth rate resulting from the homoepitaxy conditions, which was around 4.5  
8  $\text{nm}\cdot\text{min}^{-1}$ . The difference between the rectangular profile and the  $^{13}\text{C}$  SIMS depth profile as  
9 deconvoluted using this DRF was of the same order as the noise level and justified the use of a box-like  
10 rectangular function.

11           Fig. 3 shows the SIMS boron concentration profile ( $\text{P}_{\text{SIMS}}^{11\text{B}}$ ) along with the estimated position of the  
12 delta layer deduced from the fit of the  $^{13}\text{C}$  DRF. This  $\text{P}_{\text{SIMS}}^{11\text{B}}$  data was fitted by the convolution of the  $^{13}\text{C}$   
13 DRF and of a trapezoid function instead of a rectangular function, in order to take into account a  
14 possible mismatch. The nominal concentration of the estimated real dopant depth profile was  
15 determined from the integral under the SIMS boron concentration depth profile. For this operation, the  
16 parameters of the  $^{13}\text{C}$  DRF were not modified. The reduction of the error between the fitting curve and  
17 the data was carried out by varying the trapezoid shape, i.e., by the optimization of rising and falling  
18 edge widths; the nominal concentration was supposed to be constant. Finally, the dopant boron  
19 concentration depth profile ( $\text{P}_{\text{Dopant}}^{11\text{B}}$ ) was deduced from the trapezoid function modulated by the Gaussian  
20 filtered noise resulting in the error fit and an offset of  $2\cdot 10^{17}$   $\text{at}\cdot\text{cm}^{-3}$ . Such a tentative deconvolution  
21 was made on finite elements, which depend on the spacing of the depth points recorded by SIMS. This  
22 procedure consequently introduces some errors, especially visible when the noise level is high. In this  
23 experiment, the SIMS energy was too high and the sputtering too fast to obtain a resolution good  
24 enough for precisely fitting the edge of the delta layer. However, after this DRF treatment, the boron

1 profile was found to be 5 to 7 times sharper than before; the initially measured 1.5 nm/dec rising edge  
2 became 0.3 nm/dec after fitting. This fitting gave the possibility of detecting a depth shift between the  
3 concentration profiles of carbon and boron atoms (see Fig. 3). This could be coming from the late  
4 boron incorporation (an 1.6 nm-thick edge shift corresponds to a delay of 20 s for the gas mixture to  
5 reach the nominal boron concentration on the diamond-growing surface) at the beginning of the boron-  
6 delta layer growth, and from the residual boron contamination during the intrinsic cap-layer overgrowth.

7 In summary, we succeeded in extracting the depth resolution function (DRF) from a  
8 synchronized B and  $^{13}\text{C}$  diamond delta structure. By DRF deconvolution treatments, the broadening  
9 induced by ion mixing has been reduced; the SIMS resolution has been improved and reached the  
10 nanometer range. This allows a more reliable characterization by SIMS of nanometer-thin diamond-  
11 embedded layers, containing specific doping (boron, nitrogen, or phosphorus), over many orders of  
12 magnitude in concentration. For these reasons, the isotopic diamond delta structure is a powerful  
13 calibration tool for SIMS.

14

15 **Acknowledgments** The financial support of Agence Nationale de la Recherche under contract ANR08-  
16 BLAN-0195 and la Région Rhône-Alpes for the bourse de mobilité Explora'Doc are gratefully  
17 acknowledged. This work was also supported by the Strategic International Collaborative Research  
18 Project from the Japan Science and Technology Agency, and a Grant-in-Aid for Scientific Research  
19 from the Japan Society for the Promotion of Science (No. 18760241). The authors would like to  
20 express their deep gratitude to Professor G. Prudon for his kind expert advice on the depth resolution  
21 function treatment by isotope enrichment.



## References

- 1) H. Umezawa, M. Nagase, Y. Kato, and S. Shikata: *Diamond Relat. Mater.* **24** (2012) 201.
- 2) T. Ishikawa, K.-M. C. Fu, C. Santori, V. M. Acosta, R. G. Beausoleil, H. Watanabe, S. Shikata, and K. M. Itoh: *Nano Lett.* **12** (2012) 2083.
- 3) K. Ohno, F. J. Heremans, L. C. Bassett, B. A. Myers, D. M. Toyli, A. C. Bleszynski Jayich, C. J. Palmstrøm, and D. D. Awschalom: *Appl. Phys. Lett.* **101** (2012) 082413.
- 4) R. Edgington, S. Sato, Y. Ishiyama, R. Morris, R. B. Jackman, and H. Kawarada: *J. Appl. Phys.* **111** (2012) 033710.
- 5) A. Fiori, T. N. Tran Thi, G. Chicot, F. Jomard, F. Omnès, E. Gheeraert, and E. Bustarret: *Diamond Relat. Mater.* **24** (2012) 175.
- 6) S. Hofmann: *App. Phys.* **13** (1977) 205.
- 7) R. S. Balmer, I. Friel, S. Heppelstone, J. Isberg, M. J. Uren, M. L. Markham, N. L. Palmer, J. Pilkington, P. Huggett, S. Majdi, and R. Lang: *J. Appl. Phys.* **113** (2013) 033702.
- 8) Y. Shimizu, H. Takamizawa, Y. Kawamura, M. Uematsu, T. Toyama, K. Inoue, E. E. Haller, K. M. Itoh, and Y. Nagai: *J. Appl. Phys.* **113** (2013) 026101.
- 9) D. Araujo, P. Achatz, R. El Bouayadi, A. J. Garcia, M. P. Alegre, M. P. Villar, F. Jomard, and E. Bustarret: *Diamond Relat. Mater.* **19** (2010) 972.
- 10) Y.-G. Lu, S. Turner, J. Verbeeck, S. D. Janssens, P. Wagner, K. Haenen, and G. Van Tendeloo: *Appl. Phys. Lett.* **101** (2012) 041907.
- 11) G. Chicot, T. N. Thu Nhi, A. Fiori, F. Jomard, E. Gheeraert, E. Bustarret, and J. Pernot: *Appl. Phys Lett.* **101** (2012) 162101.
- 12) Y. Shimizu, A. Takano, and K. M. Itoh: *Appl. Surf. Sci.* **255** (2008) 1345.
- 13) H. Watanabe, and S. Shikata: *Diamond Relat. Mater.* **20** (2011) 980.
- 14) M. G. Dowsett, G. Rowlands, P. N. Allen, and D. Barlow: *Surf. Interface Anal.* **21** (1994) 310.
- 15) B. Gautier, R. Prost, G. Prudon, and J. C. Dupuy: *Surf. Interface Anal.* **24** (1996) 733.
- 16) T. Teraji, T. Taniguchi, S. Koizumi, K. Watanabe, M. Liao, Y. Koide, and J. Isoya: *Jpn. J. Appl. Phys.* **51** (2012) 090104.
- 17) J. F. Ziegler: *SRIM 1984-2013*.

**Caption Fig. 1.**

Simulations of SIMS depth profiles corresponding to (a) a Dirac delta function (pink vertical line localized at 47 nm below the surface) with the corresponding DRF (yellow filled black line) and (b) a 14 nm-thick layer (pink filled box) with the corresponding DRF convolution (construction elements symbolized by the yellow pattern). On such profiles, the surface lies on the left at “0” depth.

**Caption Fig. 2.**

Depth profiles for  $^{13}\text{C}$  concentrations in the diamond delta structure, plotted in linear (left) and semilog (right) scales. The SIMS intensity depth profile ( $P_{\text{SIMS}}^{13\text{C}}$ ) is represented by purple dots; the dashed black line follows the corresponding fit by the convolution of the DRF, and square input signal. The DRF is plotted as a solid blue line and the  $^{13}\text{C}$  dopant profile ( $P_{\text{Dopant}}^{13\text{C}}$ ) corresponding to the deconvolution of  $P_{\text{SIMS}}^{13\text{C}}$  by the DRF is plotted in orange.

**Caption Fig. 3.**

Depth profiles related to  $^{11}\text{B}$  in the diamond delta structure plotted in linear (left) and semilog scales. Light green and black dots follow the SIMS boron concentration profile ( $P_{\text{SIMS}}^{11\text{B}}$ ) and the deconvoluted boron dopant profile ( $P_{\text{Dopant}}^{11\text{B}}$ ) respectively. The orange box indicates the position of the delta layer based on the  $^{13}\text{C}$  dopant profile.

**Table I.** Parameters of the DRF used in the fitting process.  $\text{Cs}^+$  primary ions were used at 14.5 keV, and the incidence angle was  $27^\circ$  in a Cameca IMS 4f.

$\lambda_{up}$ (nm)	$\lambda_{down}$ (nm)	$\sigma$ (nm)	$z_0$ (nm)	$\delta$ (nm)
0.9	3.0	0.6	47	14

Fig. 1.

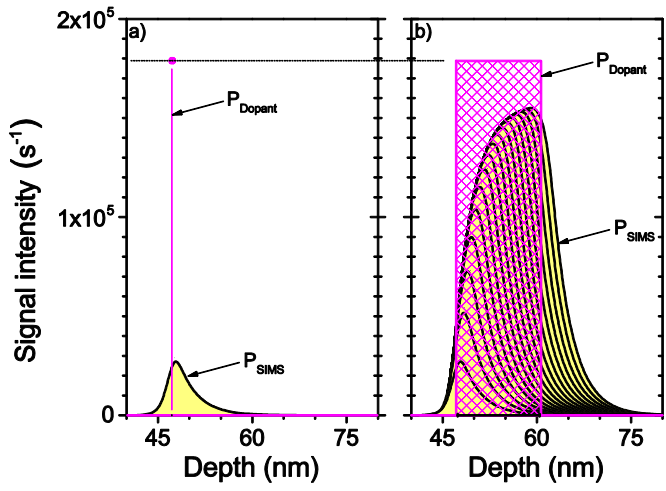


Fig. 2.

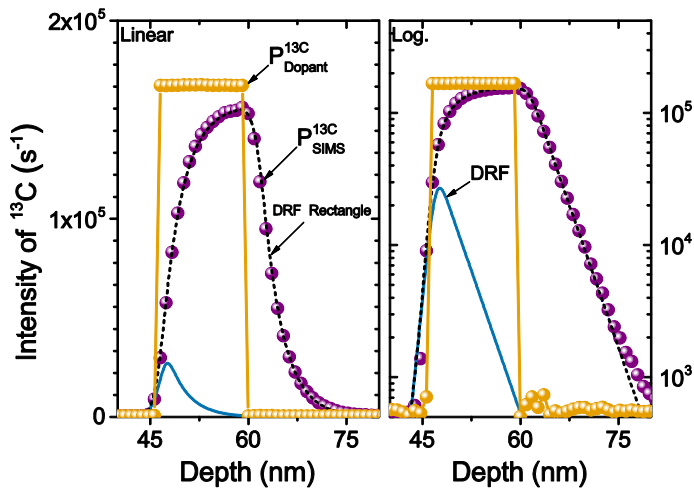


Fig. 3.

