



HAL
open science

Poly[[hexaaquasesqui(μ -benzene-1,2,4,5-tetracarboxylato) dicopper(II)disodium] monohydrate]

Magatte Camara, Mohamed Fadel Keita, Cherif Cheikh Samsidine Cisse,
Carole Daiguebonne, Olivier Guillou

► **To cite this version:**

Magatte Camara, Mohamed Fadel Keita, Cherif Cheikh Samsidine Cisse, Carole Daiguebonne, Olivier Guillou. Poly[[hexaaquasesqui(μ -benzene-1,2,4,5-tetracarboxylato) dicopper(II)disodium] monohydrate]. Acta Crystallographica Section E: Structure Reports Online [2001-2014], 2014, E70, pp.m284-m285. 10.1107/S1600536814014755 . hal-01017496

HAL Id: hal-01017496

<https://hal.science/hal-01017496>

Submitted on 12 Sep 2014

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Poly[[hexaaquasesqui(μ -benzene-1,2,4,5-tetracarboxylato)dicopper(II)disodium] monohydrate]

Magatte Camara, Mohamed Fadel Keita, Cherif Cheikh Samsidine Cisse,
Carole Daiguebonne and Olivier Guillou

Acta Cryst. (2014). **E70**, m284–m285



IUCr Journals
CRYSTALLOGRAPHY JOURNALS ONLINE

This open-access article is distributed under the terms of the Creative Commons Attribution Licence <http://creativecommons.org/licenses/by/2.0/uk/legalcode>, which permits unrestricted use, distribution, and reproduction in any medium, provided the original authors and source are cited.



Poly[[hexaaquasesqui(μ -benzene-1,2,4,5-tetracarboxylato)dicopper(II)disodium] monohydrate]

Magatte Camara,^{a*} Mohamed Fadel Keita,^a Cherif Cheikh Samsidine Cisse,^a Carole Daiguebonne^b and Olivier Guillou^b

^aUniversité Assane Seck de Ziguinchor, LCPM-Groupe Matériaux Inorganiques: Chimie Douce et Cristallographie, BP 523 Ziguinchor, Senegal, and ^bINSA, UMR 6226 "Institut des Sciences Chimiques de Rennes", F-35708 Rennes, France
Correspondence e-mail: mcamara@univ-zig.sn


Received 12 May 2014; accepted 23 June 2014

Key indicators: single-crystal X-ray study; $T = 293$ K; mean $\sigma(\text{C}-\text{C}) = 0.004$ Å; H-atom completeness 77%; R factor = 0.049; wR factor = 0.144; data-to-parameter ratio = 22.6.

In the title compound, $\{[\text{Cu}_2\text{Na}_2(\text{C}_{10}\text{H}_2\text{O}_8)_{1.5}(\text{H}_2\text{O})_6]\cdot\text{H}_2\text{O}\}_n$, the Cu^{2+} ion is hexacoordinated by five O atoms from benzene-1,2,4,5-tetracarboxylate (btec^{4-}) ligands and one water molecule. The Na^+ ion is also hexacoordinated, by four O atoms from btec^{4-} ligands and two water molecules. One of the two btec^{4-} molecules sits on a crystallographic inversion centre. CuO_6 and NaO_6 octahedra are connected, forming bi-dimensional layers. These layers, which extend parallel to the ac plane, are further interconnected by μ_{10} - or μ_{11} -bridging btec^{4-} ligands and by $\text{O}-\text{H}\cdots\text{O}$ hydrogen bonds, involving both btec^{4-} ligands and water molecules, forming a three-dimensional network.

Related literature

For related structures, see: Camara *et al.* (2013); Luo *et al.* (2013); Gong & Zhang (2011); Liu *et al.* (2010); Zhang *et al.* (2007). For related crystal-growth methods in gels, see: Henisch (1988); Henisch & Roy (1970); Daiguebonne *et al.* (2003).

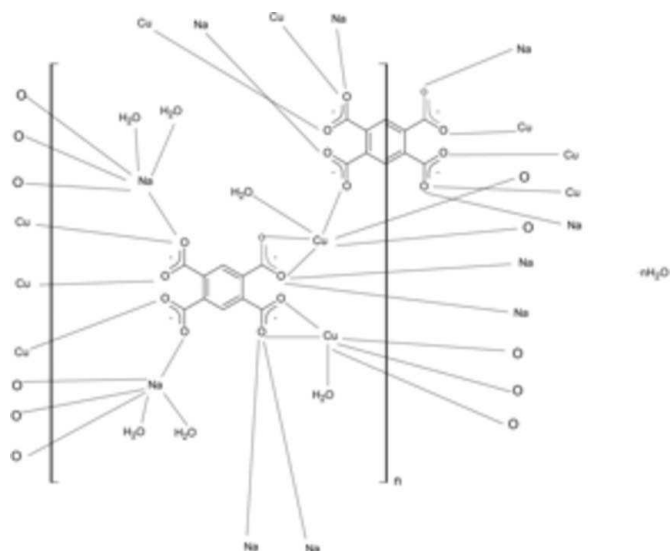

Experimental

Crystal data

$[\text{Cu}_2\text{Na}_2(\text{C}_{10}\text{H}_2\text{O}_8)_{1.5}(\text{H}_2\text{O})_6]\cdot\text{H}_2\text{O}$
 $M_r = 674.34$
 Monoclinic, $P2_1/c$
 $a = 8.0844$ (1) Å
 $b = 16.9103$ (3) Å
 $c = 15.6815$ (3) Å
 $\beta = 98.055$ (1)°

$V = 2122.66$ (6) Å³
 $Z = 4$
 Mo $K\alpha$ radiation
 $\mu = 2.15$ mm⁻¹
 $T = 293$ K
 $0.11 \times 0.08 \times 0.07$ mm

Data collection

Bruker APEXII diffractometer
 Absorption correction: multi-scan (SADABS; Bruker, 2007)
 $T_{\min} = 0.701$, $T_{\max} = 0.848$

34613 measured reflections
 8438 independent reflections
 4356 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.058$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.049$
 $wR(F^2) = 0.144$
 $S = 0.94$
 8438 reflections
 373 parameters
 15 restraints

H atoms treated by a mixture of independent and constrained refinement
 $\Delta\rho_{\max} = 1.49$ e Å⁻³
 $\Delta\rho_{\min} = -1.02$ e Å⁻³

Table 1

Hydrogen-bond geometry (Å, °).

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
$\text{O4}-\text{H42}\cdots\text{O11}^{\text{i}}$	0.81 (2)	1.93 (2)	2.737 (3)	174 (4)
$\text{O2}-\text{H22}\cdots\text{O511}$	0.82 (2)	1.91 (2)	2.697 (3)	162 (4)
$\text{O1}-\text{H11}\cdots\text{O812}$	0.80 (2)	1.95 (2)	2.708 (3)	159 (4)
$\text{O2}-\text{H21}\cdots\text{OW1}^{\text{ii}}$	0.78 (2)	1.85 (2)	2.618 (3)	167 (4)
$\text{O5}-\text{H51}\cdots\text{O512}^{\text{iii}}$	0.87 (2)	1.91 (2)	2.744 (3)	161 (4)
$\text{O1}-\text{H12}\cdots\text{O2}^{\text{iv}}$	0.81 (2)	1.99 (2)	2.794 (3)	176 (4)
$\text{O3}-\text{H32}\cdots\text{O1}^{\text{v}}$	0.85 (2)	2.36 (3)	2.977 (3)	130 (3)

Symmetry codes: (i) $x - 1, y, z$; (ii) $-x - 1, y + \frac{1}{2}, -z + \frac{3}{2}$; (iii) $x, -y + \frac{1}{2}, z - \frac{1}{2}$; (iv) $x + 1, y, z$; (v) $-x, y - \frac{1}{2}, -z + \frac{3}{2}$.

Data collection: APEX2 (Bruker, 2007); cell refinement: SAINT (Bruker, 2007); data reduction: SAINT; program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL2014 (Sheldrick, 2008); molecular graphics:

DIAMOND (Brandenburg, 1999); software used to prepare material for publication: *publCIF* (Westrip, 2010).

The French Cooperation Agency in Senegal is acknowledged for financial support. The X-ray Diffraction Centre of the University of Rennes is acknowledged for the data collection.

Supporting information for this paper is available from the IUCr electronic archives (Reference: PK2525).

References

- Brandenburg, K. (1999). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
- Bruker (2007). *APEX2*, *SAINT* and *SADABS*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Camara, M., Tine, M., Daiguebonne, C., Guillou, O. & Roisnel, T. (2013). *Acta Cryst.* **E69**, m680–m681.
- Daiguebonne, C., Deluzet, A., Camara, M., Boubekeur, K., Audebrand, N., Gerault, Y., Baux, C. & Guillou, O. (2003). *Cryst. Growth Des.* **3**, 1015–1020.
- Gong, X. Y. & Zhang, L. (2011). *Acta Cryst.* **E67**, m736.
- Henisch, H. K. (1988). In *Crystals Growth in Gels and Liesegang Rings*. Cambridge University Press.
- Henisch, H. K. & Roy, R. (1970). In *Crystals Growth in Gels*. The Pennsylvania State University Press.
- Liu, H. K., Tsao, T. H., Lin, C. H. & Zima, V. (2010). *CrystEngComm*, **12**, 1044–1047.
- Luo, Y., Bernot, K., Calvez, G., Freslon, S., Daiguebonne, C., Guillou, O., Kerbellec, N. & Roisnel, T. (2013). *CrystEngComm*, **15**, 1882–1896.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Westrip, S. P. (2010). *J. Appl. Cryst.* **43**, 920–925.
- Zhang, D. J., Song, T. Y., Zhang, P., Shi, J., Wang, Y., Wang, L., Ma, K. R., Yin, W. R., Zhao, J., Fan, Y. & Xu, J. N. (2007). *Inorg. Chem. Commun.* **10**, 876–879.

supporting information

Acta Cryst. (2014). E70, m284–m285 [doi:10.1107/S1600536814014755]

Poly[[hexaaquasesqui(μ -benzene-1,2,4,5-tetracarboxylato)dicopper(II)disodium] monohydrate]

Magatte Camara, Mohamed Fadel Keita, Cherif Cheikh Samsidine Cisse, Carole Daignebonne and Olivier Guillou

1. Comment

In recent years, much attention has been paid to coordination polymers that involve covalent bonds or supramolecular contacts. A huge number of novel compounds with interesting crystal structures and topologies have been reported. As part of this research, benzene-1,2,4,5-tetracarboxylate (btec^{4-}) can be used as a ligand to form various supramolecular architectures through its four rigid carboxyl groups [see Camara *et al.* (2013), Luo *et al.* (2013), Gong & Zhang (2011), Liu *et al.* (2010), Zhang *et al.* (2007)]. In order to enrich this family of compounds, we recently undertook a study devoted to reactions of H_4btec with metal ions in gel media. In particular, we were interested in such reactions with agar-agar gel bridges in U-shaped tubes, and we have successfully synthesized a novel polymeric complex from H_4btec and copper (II) chloride. We report here the synthesis and the crystal structure of the title coordination polymer. As shown in Fig. 1, the asymmetric unit of the title compound contains two Cu(II) ions, two Na(I) ions, coordinated water molecules and three btec^{4-} ligands. One of the two crystallographically distinct btec^{4-} ligands is located on an inversion centre. One btec^{4-} ligand acts as a m_{10} -bridge that links six Cu(II) ions and four Na(I) ions, while the other acts as a m_{11} -bridge that links five Cu(II) ions and six Na(I) ions. Cu(II) ions are hexa-coordinated by five O atoms from four btec^{4-} ligands and one O atom from a water molecule, while Na(I) ions are hexa-coordinated by four O atoms from four btec^{4-} ligands and two O atoms from two water molecules. As shown in Fig. 2, two-dimensional Cu–O–Na layers extend parallel to the ac plane. Furthermore, these two-dimensional layers are interconnected by m_{10} - or m_{11} -bridging btec^{4-} ligands and by O—H \cdots O hydrogen bonds, forming a three-dimensional framework.

2. Experimental

All reagents were used as obtained without further purification. Copper (II) chloride was purchased from STREM Chemicals. 1,2,4,5-benzenetetracarboxylic acid was purchased from Acros Organics. Its sodium salt was prepared by addition of four equivalents of sodium hydroxide to a suspension of 1,2,4,5-benzenetetracarboxylic acid in de-ionized water until complete dissolution. Then, the solution was evaporated to dryness. The solid phase was then put in suspension in ethanol, stirred and refluxed for 1 h. After filtration and drying in a desiccator, a white powder of tetrasodium 1,2,4,5-benzene-tetra-carboxylate was obtained (yield = 90%). Single crystals of the coordination polymer were obtained by slow diffusion of dilute aqueous solutions of Cu(II) chloride (0.25 mmol in 20mL) and of the sodium salt of 1,2,4,5-benzenetetra-carboxylic acid (0.25 mmol in 20mL) through agar-agar gel bridges in U-shaped tubes. The gel was purchased from Acros Organics and gelled according to established procedure [see for example, Henisch *et al.* (1988), Henisch *et al.* (1970), Daignebonne *et al.* (2003)]. After several weeks, colorless single crystals were obtained.

3. Refinement

The H-atoms from water molecules that could be found in difference maps were included with constrained coordinates. Some hydrogen atoms could not be reliably located, so these have only been taken into account in the formula (*i.e.* not in the model).

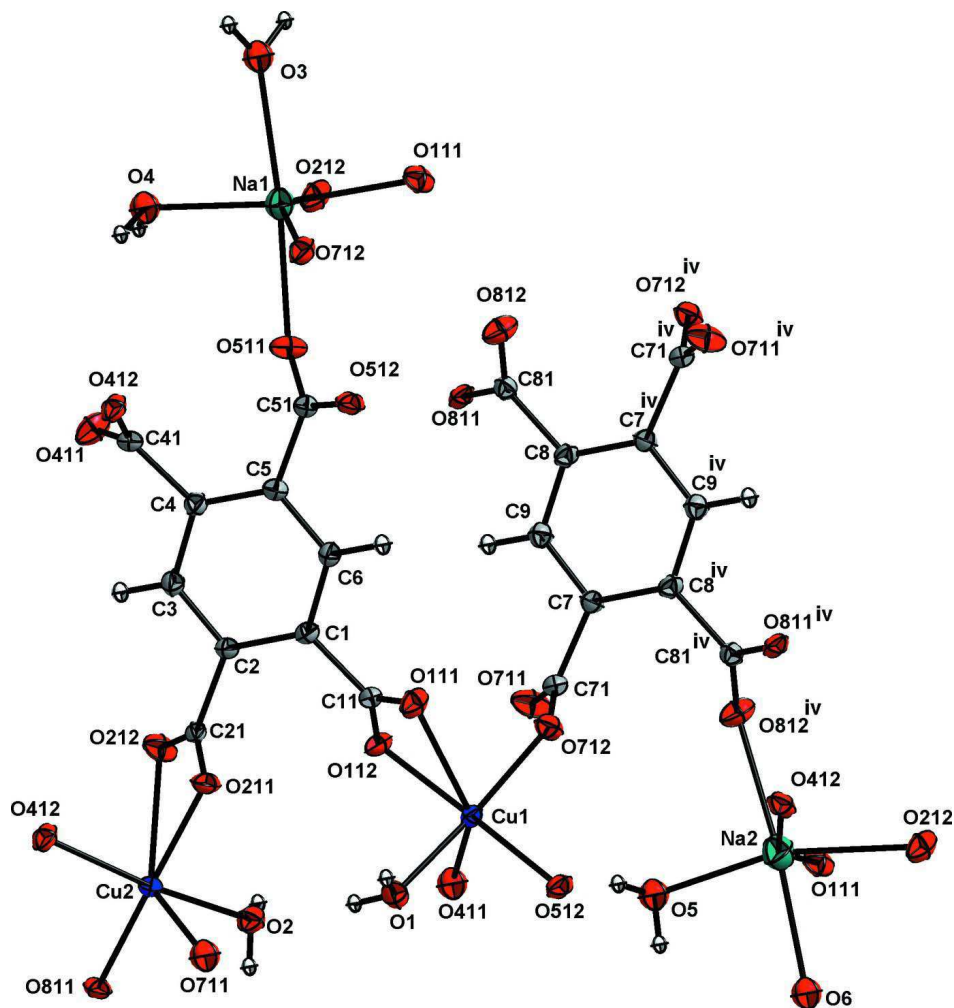


Figure 1

Extended asymmetric unit of the title compound, with the atom-numbering scheme. Displacement ellipsoids are drawn at the 50% probability level. [Symmetry code: (iv) $x, -y + 1/2, z - 1/2$.]

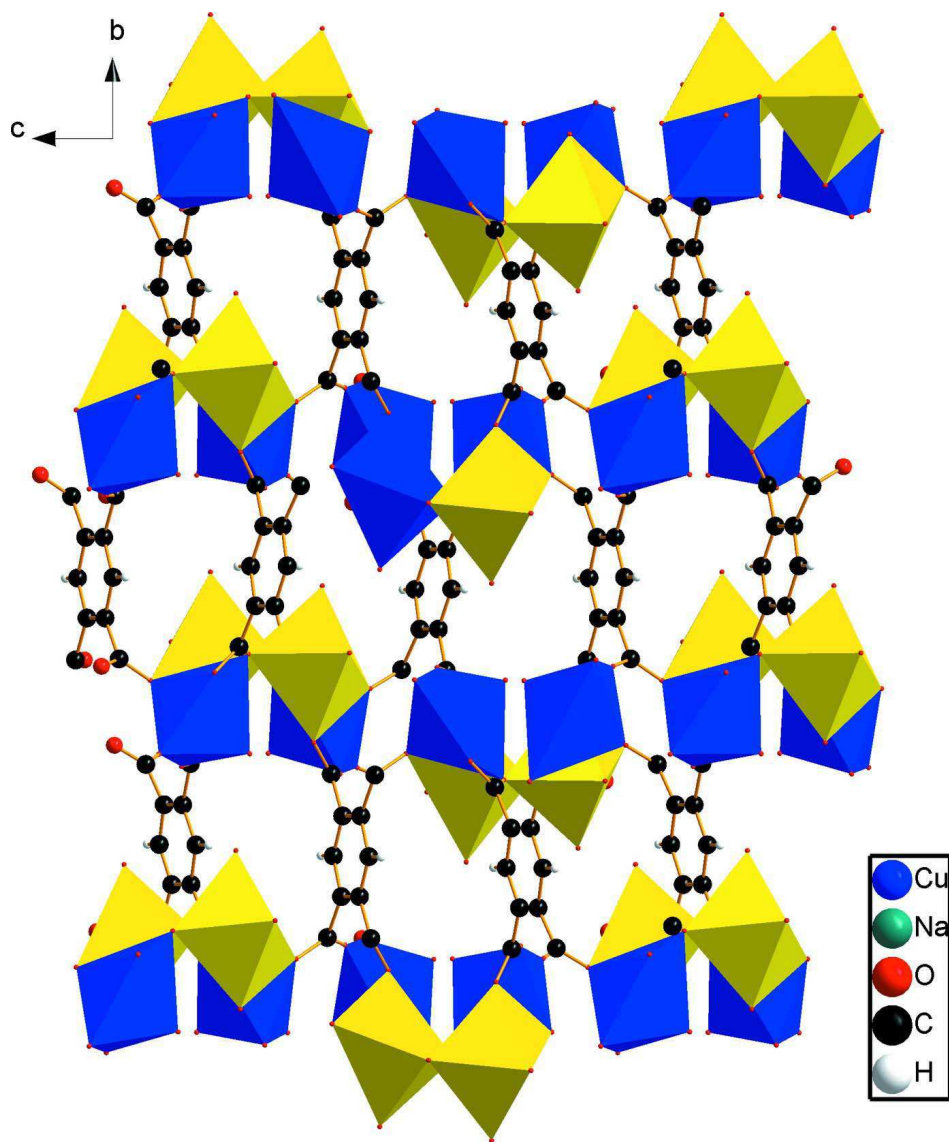


Figure 2

A view of the three-dimensional network of the title compound, projected perpendicular to the *bc*-plane.

Poly[[hexaaquasesqui(μ -benzene-1,2,4,5-tetracarboxylato)dicopper(II)disodium] monohydrate]

Crystal data

$[\text{Cu}_2\text{Na}_2(\text{C}_{10}\text{H}_2\text{O}_8)_{1.5}(\text{H}_2\text{O})_6] \cdot \text{H}_2\text{O}$

$M_r = 674.34$

Monoclinic, $P2_1/c$

$a = 8.0844 (1) \text{ \AA}$

$b = 16.9103 (3) \text{ \AA}$

$c = 15.6815 (3) \text{ \AA}$

$\beta = 98.055 (1)^\circ$

$V = 2122.66 (6) \text{ \AA}^3$

$Z = 4$

$F(000) = 1356$

$D_x = 2.110 \text{ Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$

Cell parameters from 31092 reflections

$\theta = 2.9\text{--}32.0^\circ$

$\mu = 2.15 \text{ mm}^{-1}$

$T = 293 \text{ K}$

Cobblestone, blue

$0.11 \times 0.08 \times 0.07 \text{ mm}$

Data collection

Bruker APEXII diffractometer	34613 measured reflections
Radiation source: Fine-focus sealed tube	8438 independent reflections
Graphite monochromator	4356 reflections with $I > 2\sigma(I)$
CCD rotation images, thin slices scans	$R_{\text{int}} = 0.058$
Absorption correction: multi-scan	$\theta_{\text{max}} = 34.8^\circ, \theta_{\text{min}} = 3.5^\circ$
(SADABS; Bruker, 2007)	$h = -11 \rightarrow 12$
$T_{\text{min}} = 0.701, T_{\text{max}} = 0.848$	$k = -26 \rightarrow 21$
	$l = -20 \rightarrow 24$

Refinement

Refinement on F^2	Hydrogen site location: inferred from neighbouring sites
Least-squares matrix: full	H atoms treated by a mixture of independent and constrained refinement
$R[F^2 > 2\sigma(F^2)] = 0.049$	$w = 1/[\sigma^2(F_o^2) + (0.0813P)^2]$
$wR(F^2) = 0.144$	where $P = (F_o^2 + 2F_c^2)/3$
$S = 0.94$	$(\Delta/\sigma)_{\text{max}} = 0.010$
8438 reflections	$\Delta\rho_{\text{max}} = 1.49 \text{ e } \text{\AA}^{-3}$
373 parameters	$\Delta\rho_{\text{min}} = -1.02 \text{ e } \text{\AA}^{-3}$
15 restraints	

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Cu1	0.15805 (4)	0.25569 (2)	0.80720 (2)	0.01609 (10)
Cu2	-0.45959 (4)	0.26469 (2)	0.54858 (2)	0.01697 (10)
Na1	-0.17322 (14)	0.13536 (7)	0.78727 (8)	0.0284 (3)
Na2	-0.13005 (15)	0.15430 (8)	0.56592 (9)	0.0329 (3)
O112	0.2924 (2)	0.17014 (11)	0.76659 (13)	0.0195 (4)
O211	-0.5911 (2)	0.17609 (11)	0.58371 (13)	0.0215 (4)
O1	0.1863 (2)	0.31650 (12)	0.69877 (13)	0.0224 (4)
O4	-0.4112 (3)	0.11473 (14)	0.85120 (16)	0.0316 (5)
O511	-0.2307 (2)	0.27440 (11)	0.78365 (14)	0.0256 (5)
O811	-0.3190 (2)	0.35241 (11)	0.52142 (13)	0.0204 (4)
O812	-0.0757 (2)	0.29573 (12)	0.57293 (14)	0.0271 (5)
O111	0.0408 (2)	0.13710 (12)	0.70094 (13)	0.0230 (4)
O212	-0.3474 (2)	0.13420 (12)	0.65142 (14)	0.0260 (5)
O2	-0.4857 (2)	0.31465 (12)	0.66155 (14)	0.0228 (4)
O412	-0.3727 (2)	0.19907 (11)	0.46253 (13)	0.0215 (4)
O711	0.3056 (2)	0.15899 (12)	0.98797 (15)	0.0308 (5)
O512	0.0052 (2)	0.33892 (11)	0.83143 (13)	0.0214 (4)
O411	0.3855 (2)	0.31657 (12)	0.87600 (15)	0.0317 (5)
C8	-0.0749 (3)	0.42790 (15)	0.51646 (17)	0.0166 (5)
O712	0.0771 (2)	0.18442 (11)	0.89280 (13)	0.0222 (4)
C5	-0.2469 (3)	0.40780 (15)	0.82911 (17)	0.0172 (5)

C81	-0.1595 (3)	0.35232 (15)	0.53885 (18)	0.0177 (5)
C51	-0.1527 (3)	0.33362 (15)	0.81388 (18)	0.0165 (5)
C7	0.0755 (3)	0.07233 (15)	0.98119 (17)	0.0167 (5)
C6	-0.1850 (3)	0.47968 (15)	0.80321 (19)	0.0191 (6)
H6	-0.0866	0.4800	0.7788	0.023*
O5	0.1040 (3)	0.13627 (18)	0.50399 (18)	0.0505 (7)
C4	-0.3963 (3)	0.09269 (15)	0.36547 (17)	0.0159 (5)
O3	-0.1803 (4)	-0.00918 (16)	0.7752 (2)	0.0556 (8)
OW1	-0.4788 (3)	-0.03675 (15)	0.88423 (19)	0.0526 (7)
C2	-0.5855 (3)	0.05086 (15)	0.64934 (18)	0.0161 (5)
C21	-0.4989 (3)	0.12554 (15)	0.62866 (17)	0.0160 (5)
C1	0.2666 (3)	0.05056 (15)	0.68709 (18)	0.0169 (5)
C9	0.1473 (3)	-0.00066 (16)	0.96511 (18)	0.0185 (5)
H9	0.2465	-0.0013	0.9414	0.022*
C11	0.1920 (3)	0.12402 (15)	0.71862 (17)	0.0166 (5)
C3	-0.4787 (3)	0.02144 (16)	0.37516 (18)	0.0194 (6)
H3	-0.5785	0.0219	0.3984	0.023*
C41	-0.4697 (3)	0.16482 (15)	0.40121 (17)	0.0159 (5)
O6	-0.1540 (4)	0.0144 (2)	0.5561 (3)	0.0822 (11)
C71	0.1614 (3)	0.14565 (15)	0.95356 (18)	0.0179 (6)
H42	-0.494 (3)	0.133 (2)	0.824 (2)	0.050*
H22	-0.425 (4)	0.300 (2)	0.7052 (17)	0.050*
H11	0.122 (3)	0.300 (2)	0.6598 (18)	0.050*
H21	-0.481 (4)	0.3594 (12)	0.650 (2)	0.050*
H51	0.088 (5)	0.153 (2)	0.4512 (14)	0.050*
H41	-0.396 (4)	0.136 (2)	0.8981 (15)	0.050*
H52	0.104 (5)	0.0878 (10)	0.499 (2)	0.050*
H31	-0.176 (5)	-0.039 (2)	0.7328 (16)	0.050*
H12	0.282 (2)	0.318 (2)	0.690 (2)	0.050*
H32	-0.166 (5)	-0.0448 (19)	0.8137 (18)	0.050*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Cu1	0.01508 (17)	0.01221 (17)	0.0216 (2)	0.00191 (11)	0.00483 (13)	-0.00013 (12)
Cu2	0.01881 (18)	0.01265 (17)	0.0207 (2)	-0.00348 (11)	0.00713 (13)	-0.00177 (13)
Na1	0.0240 (6)	0.0267 (7)	0.0351 (7)	-0.0005 (5)	0.0067 (5)	0.0006 (5)
Na2	0.0270 (6)	0.0356 (7)	0.0363 (8)	0.0007 (5)	0.0054 (5)	0.0006 (6)
O112	0.0192 (9)	0.0127 (9)	0.0264 (11)	0.0019 (7)	0.0021 (8)	-0.0046 (8)
O211	0.0209 (10)	0.0132 (9)	0.0307 (12)	-0.0032 (7)	0.0047 (8)	0.0029 (8)
O1	0.0197 (10)	0.0255 (11)	0.0226 (11)	0.0017 (8)	0.0057 (8)	0.0037 (9)
O4	0.0267 (12)	0.0390 (14)	0.0286 (13)	0.0027 (9)	0.0022 (9)	-0.0038 (10)
O511	0.0274 (11)	0.0149 (10)	0.0328 (13)	0.0023 (8)	-0.0015 (9)	-0.0042 (8)
O811	0.0189 (10)	0.0136 (9)	0.0297 (12)	-0.0050 (7)	0.0063 (8)	0.0008 (8)
O812	0.0270 (11)	0.0190 (11)	0.0338 (13)	-0.0015 (8)	-0.0015 (9)	0.0063 (9)
O111	0.0161 (10)	0.0230 (11)	0.0296 (12)	0.0032 (7)	0.0020 (8)	-0.0030 (8)
O212	0.0175 (10)	0.0261 (11)	0.0338 (13)	-0.0070 (8)	0.0015 (8)	0.0023 (9)
O2	0.0277 (11)	0.0203 (10)	0.0203 (12)	-0.0015 (8)	0.0034 (8)	-0.0017 (9)

O412	0.0198 (9)	0.0197 (10)	0.0255 (11)	-0.0020 (7)	0.0050 (8)	-0.0092 (8)
O711	0.0218 (11)	0.0276 (12)	0.0405 (14)	-0.0103 (8)	-0.0042 (9)	0.0035 (10)
O512	0.0171 (10)	0.0147 (10)	0.0330 (12)	0.0031 (7)	0.0058 (8)	-0.0023 (8)
O411	0.0262 (11)	0.0282 (12)	0.0390 (14)	-0.0121 (9)	-0.0016 (9)	0.0025 (10)
C8	0.0179 (13)	0.0145 (13)	0.0174 (14)	-0.0042 (9)	0.0030 (10)	-0.0013 (10)
O712	0.0223 (10)	0.0199 (10)	0.0246 (11)	-0.0003 (8)	0.0041 (8)	0.0056 (8)
C5	0.0199 (13)	0.0132 (13)	0.0193 (14)	0.0023 (9)	0.0054 (10)	-0.0002 (10)
C81	0.0181 (13)	0.0167 (13)	0.0194 (14)	-0.0027 (10)	0.0064 (10)	-0.0046 (10)
C51	0.0186 (13)	0.0138 (13)	0.0179 (14)	0.0020 (9)	0.0054 (10)	0.0009 (10)
C7	0.0145 (12)	0.0146 (13)	0.0213 (15)	0.0004 (9)	0.0039 (10)	0.0033 (10)
C6	0.0184 (13)	0.0157 (13)	0.0251 (16)	0.0001 (10)	0.0096 (11)	0.0026 (11)
O5	0.0407 (15)	0.075 (2)	0.0365 (16)	-0.0024 (15)	0.0076 (12)	0.0115 (15)
C4	0.0162 (12)	0.0153 (13)	0.0167 (14)	-0.0008 (9)	0.0038 (10)	-0.0028 (10)
O3	0.0532 (16)	0.0305 (15)	0.087 (2)	0.0089 (12)	0.0230 (17)	0.0051 (15)
OW1	0.0622 (17)	0.0350 (15)	0.0592 (19)	-0.0121 (12)	0.0036 (14)	-0.0014 (13)
C2	0.0168 (12)	0.0116 (12)	0.0203 (14)	-0.0009 (9)	0.0045 (10)	0.0001 (10)
C21	0.0177 (13)	0.0132 (12)	0.0188 (14)	-0.0041 (9)	0.0082 (10)	-0.0055 (10)
C1	0.0184 (13)	0.0131 (12)	0.0200 (14)	-0.0001 (9)	0.0049 (10)	-0.0026 (10)
C9	0.0160 (13)	0.0173 (13)	0.0227 (15)	0.0010 (10)	0.0050 (10)	0.0021 (11)
C11	0.0217 (14)	0.0110 (12)	0.0185 (14)	0.0004 (10)	0.0076 (10)	-0.0002 (10)
C3	0.0172 (13)	0.0194 (14)	0.0228 (15)	-0.0013 (10)	0.0074 (11)	-0.0037 (11)
C41	0.0181 (13)	0.0113 (12)	0.0186 (14)	-0.0013 (9)	0.0036 (10)	0.0006 (10)
O6	0.068 (2)	0.073 (2)	0.106 (3)	-0.0037 (17)	0.015 (2)	-0.015 (2)
C71	0.0219 (14)	0.0115 (12)	0.0217 (15)	0.0003 (10)	0.0077 (11)	0.0000 (10)

Geometric parameters (Å, °)

Cu1—O512	1.9450 (17)	O111—C11	1.235 (3)
Cu1—O112	1.9676 (17)	O212—C21	1.235 (3)
Cu1—O712	1.9821 (19)	O412—C41	1.290 (3)
Cu1—O1	2.027 (2)	O711—C71	1.235 (3)
Cu1—O411	2.247 (2)	O711—Cu2 ⁱⁱ	2.380 (2)
Cu1—Na1	3.3431 (12)	O512—C51	1.271 (3)
Cu2—O412	1.9523 (18)	O411—C41 ⁱⁱ	1.223 (3)
Cu2—O811	1.9519 (17)	C8—C9 ⁱⁱⁱ	1.390 (4)
Cu2—O211	1.9603 (18)	C8—C7 ^{iv}	1.404 (3)
Cu2—O2	2.000 (2)	C8—C81	1.514 (3)
Cu2—O711 ⁱ	2.380 (2)	O712—C71	1.273 (3)
Cu2—Na2	3.2331 (13)	C5—C6	1.396 (4)
Na1—O4	2.317 (2)	C5—C4 ^v	1.406 (3)
Na1—O111	2.342 (2)	C5—C51	1.504 (3)
Na1—O212	2.384 (2)	C7—C8 ^v	1.404 (3)
Na1—O511	2.396 (2)	C7—C9	1.402 (4)
Na1—O3	2.452 (3)	C7—C71	1.514 (3)
Na1—O712	2.566 (2)	C6—C1 ⁱⁱⁱ	1.387 (4)
Na1—Na2	3.5514 (19)	C4—C3	1.396 (4)
Na2—O5	2.266 (3)	C4—C5 ^{iv}	1.406 (3)
Na2—O6	2.377 (4)	C4—C41	1.499 (3)

Na2—O212	2.379 (2)	C2—C3 ^{vi}	1.403 (3)
Na2—O111	2.378 (2)	C2—C1 ^{vii}	1.407 (4)
Na2—O812	2.431 (2)	C2—C21	1.501 (3)
Na2—O412	2.482 (2)	C1—C6 ^{viii}	1.387 (4)
O112—C11	1.289 (3)	C1—C2 ^{ix}	1.407 (4)
O211—C21	1.279 (3)	C1—C11	1.495 (3)
O511—C51	1.241 (3)	C9—C8 ^{viii}	1.390 (4)
O811—C81	1.280 (3)	C3—C2 ^{vi}	1.403 (3)
O812—C81	1.248 (3)	C41—O411 ⁱ	1.223 (3)
O512—Cu1—O112	171.78 (8)	O5—Na2—Cu2	140.32 (9)
O512—Cu1—O712	91.64 (8)	O6—Na2—Cu2	120.71 (9)
O112—Cu1—O712	91.24 (8)	O212—Na2—Cu2	57.65 (5)
O512—Cu1—O1	86.91 (8)	O111—Na2—Cu2	120.96 (6)
O112—Cu1—O1	88.24 (8)	O812—Na2—Cu2	65.00 (5)
O712—Cu1—O1	164.40 (8)	O412—Na2—Cu2	37.09 (4)
O512—Cu1—O411	94.25 (8)	O5—Na2—Na1	127.53 (9)
O112—Cu1—O411	92.33 (8)	O6—Na2—Na1	87.46 (10)
O712—Cu1—O411	106.20 (8)	O212—Na2—Na1	41.83 (6)
O1—Cu1—O411	89.40 (8)	O111—Na2—Na1	40.82 (5)
O512—Cu1—Na1	86.34 (6)	O812—Na2—Na1	94.95 (6)
O112—Cu1—Na1	89.62 (6)	O412—Na2—Na1	119.28 (6)
O712—Cu1—Na1	49.99 (6)	Cu2—Na2—Na1	86.65 (3)
O1—Cu1—Na1	114.41 (6)	C11—O112—Cu1	107.64 (15)
O411—Cu1—Na1	156.16 (6)	C21—O211—Cu2	111.63 (16)
O412—Cu2—O811	90.24 (8)	C51—O511—Na1	134.11 (18)
O412—Cu2—O211	91.24 (8)	C81—O811—Cu2	123.53 (17)
O811—Cu2—O211	176.00 (8)	C81—O812—Na2	130.61 (18)
O412—Cu2—O2	160.91 (9)	C11—O111—Na1	131.02 (19)
O811—Cu2—O2	90.52 (8)	C11—O111—Na2	130.92 (18)
O211—Cu2—O2	86.87 (8)	Na1—O111—Na2	97.59 (8)
O412—Cu2—O711 ⁱ	112.09 (8)	C21—O212—Na2	129.39 (19)
O811—Cu2—O711 ⁱ	87.53 (8)	C21—O212—Na1	134.18 (18)
O211—Cu2—O711 ⁱ	95.34 (8)	Na2—O212—Na1	96.43 (8)
O2—Cu2—O711 ⁱ	86.99 (8)	C41—O412—Cu2	122.04 (16)
O412—Cu2—Na2	50.05 (6)	C41—O412—Na2	133.81 (17)
O811—Cu2—Na2	87.65 (6)	Cu2—O412—Na2	92.86 (8)
O211—Cu2—Na2	90.46 (6)	C71—O711—Cu2 ⁱⁱ	157.62 (19)
O2—Cu2—Na2	110.93 (6)	C51—O512—Cu1	123.57 (17)
O711 ⁱ —Cu2—Na2	161.47 (6)	C41 ⁱⁱ —O411—Cu1	162.7 (2)
O4—Na1—O111	167.85 (10)	C9 ⁱⁱⁱ —C8—C7 ^{iv}	119.8 (2)
O4—Na1—O212	87.88 (9)	C9 ⁱⁱⁱ —C8—C81	117.9 (2)
O111—Na1—O212	82.84 (8)	C7 ^{iv} —C8—C81	122.2 (2)
O4—Na1—O511	89.31 (9)	C71—O712—Cu1	128.85 (17)
O111—Na1—O511	97.50 (8)	C71—O712—Na1	127.40 (17)
O212—Na1—O511	84.18 (8)	Cu1—O712—Na1	93.74 (8)
O4—Na1—O3	82.61 (10)	C6—C5—C4 ^v	119.1 (2)
O111—Na1—O3	88.80 (9)	C6—C5—C51	118.0 (2)

O212—Na1—O3	85.32 (11)	C4 ^v —C5—C51	122.8 (2)
O511—Na1—O3	166.98 (10)	O812—C81—O811	124.2 (2)
O4—Na1—O712	113.41 (9)	O812—C81—C8	120.7 (2)
O111—Na1—O712	77.81 (7)	O811—C81—C8	115.1 (2)
O212—Na1—O712	153.24 (8)	O511—C51—O512	125.5 (2)
O511—Na1—O712	80.26 (7)	O511—C51—C5	119.5 (2)
O3—Na1—O712	112.32 (10)	O512—C51—C5	115.0 (2)
O4—Na1—Cu1	138.94 (8)	C8 ^v —C7—C9	118.1 (2)
O111—Na1—Cu1	53.08 (5)	C8 ^v —C7—C71	124.9 (2)
O212—Na1—Cu1	116.99 (6)	C9—C7—C71	116.8 (2)
O511—Na1—Cu1	63.58 (5)	C1 ⁱⁱⁱ —C6—C5	121.7 (2)
O3—Na1—Cu1	128.59 (8)	C3—C4—C5 ^{iv}	119.3 (2)
O712—Na1—Cu1	36.27 (4)	C3—C4—C41	116.2 (2)
O4—Na1—Na2	129.62 (8)	C5 ^{iv} —C4—C41	124.3 (2)
O111—Na1—Na2	41.59 (6)	C3 ^{vi} —C2—C1 ^{vii}	118.8 (2)
O212—Na1—Na2	41.74 (5)	C3 ^{vi} —C2—C21	118.2 (2)
O511—Na1—Na2	86.20 (7)	C1 ^{vii} —C2—C21	122.9 (2)
O3—Na1—Na2	91.09 (9)	O212—C21—O211	123.9 (2)
O712—Na1—Na2	115.12 (6)	O212—C21—C2	120.7 (2)
Cu1—Na1—Na2	81.34 (3)	O211—C21—C2	115.3 (2)
O5—Na2—O6	84.46 (12)	C6 ^{viii} —C1—C2 ^{ix}	119.6 (2)
O5—Na2—O212	161.73 (11)	C6 ^{viii} —C1—C11	117.5 (2)
O6—Na2—O212	80.49 (11)	C2 ^{ix} —C1—C11	122.8 (2)
O5—Na2—O111	87.09 (9)	C8 ^{viii} —C9—C7	122.0 (2)
O6—Na2—O111	88.17 (12)	O111—C11—O112	123.0 (2)
O212—Na2—O111	82.16 (8)	O111—C11—C1	120.5 (2)
O5—Na2—O812	89.73 (10)	O112—C11—C1	116.5 (2)
O6—Na2—O812	174.00 (11)	C2 ^{vi} —C3—C4	121.5 (2)
O212—Na2—O812	104.95 (8)	O411 ⁱ —C41—O412	125.4 (2)
O111—Na2—O812	90.07 (8)	O411 ⁱ —C41—C4	120.0 (2)
O5—Na2—O412	113.10 (10)	O412—C41—C4	114.4 (2)
O6—Na2—O412	102.21 (11)	O711—C71—O712	127.3 (2)
O212—Na2—O412	80.39 (7)	O711—C71—C7	117.9 (2)
O111—Na2—O412	157.86 (8)	O712—C71—C7	114.7 (2)
O812—Na2—O412	81.41 (7)		

Symmetry codes: (i) $x-1, -y+1/2, z-1/2$; (ii) $x+1, -y+1/2, z+1/2$; (iii) $-x, y+1/2, -z+3/2$; (iv) $x, -y+1/2, z-1/2$; (v) $x, -y+1/2, z+1/2$; (vi) $-x-1, -y, -z+1$; (vii) $x-1, y, z$; (viii) $-x, y-1/2, -z+3/2$; (ix) $x+1, y, z$.

Hydrogen-bond geometry (\AA , $^\circ$)

<i>D</i> —H \cdots <i>A</i>	<i>D</i> —H	H \cdots <i>A</i>	<i>D</i> \cdots <i>A</i>	<i>D</i> —H \cdots <i>A</i>
O4—H42 \cdots O112 ^{vii}	0.81 (2)	1.93 (2)	2.737 (3)	174 (4)
O2—H22 \cdots O511	0.82 (2)	1.91 (2)	2.697 (3)	162 (4)
O1—H11 \cdots O812	0.80 (2)	1.95 (2)	2.708 (3)	159 (4)
O2—H21 \cdots OW1 ^x	0.78 (2)	1.85 (2)	2.618 (3)	167 (4)
O5—H51 \cdots O512 ^{iv}	0.87 (2)	1.91 (2)	2.744 (3)	161 (4)

O1—H12···O2 ^{ix}	0.81 (2)	1.99 (2)	2.794 (3)	176 (4)
O3—H32···O1 ^{viii}	0.85 (2)	2.36 (3)	2.977 (3)	130 (3)

Symmetry codes: (iv) $x, -y+1/2, z-1/2$; (vii) $x-1, y, z$; (viii) $-x, y-1/2, -z+3/2$; (ix) $x+1, y, z$; (x) $-x-1, y+1/2, -z+3/2$.