

Molecular brass: Cu Zn , a ligand protected superatom-like cluster.

Kerstin Freitag, Hung Banh, Christian Gemel, Rüdiger W Seidel, Samia Kahlal, Jean-Yves Saillard, Roland A Fischer

► To cite this version:

Kerstin Freitag, Hung Banh, Christian Gemel, Rüdiger W Seidel, Samia Kahlal, et al.. Molecular brass: Cu Zn , a ligand protected superatom-like cluster.. Chemical Communications, 2014, 50 (63), pp.8681-4. hal-01088478

HAL Id: hal-01088478 https://hal.science/hal-01088478

Submitted on 14 Apr 2015 $\,$

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers. L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Molecular brass: Cu₄Zn₄, A ligand protected superatom-like cluster.

Kerstin Freitag,^{*a*} Hung Banh, ^{*a*} Christian Gemel, ^{*a*} Rüdiger W. Seidel^{*a*} Samia Kahlal^{*b*}, Jean-Yves Saillard, ^{*b*} and Roland A. Fischer^{*a*,*}

* Corresponding authors

^a Inorganic Chemistry II, Ruhr-University Bochum, Universitätsstraße 150, 44801 Bochum, Germany


E-mail: roland.fischer@rub.de

^b Institut des Sciences Chimiques de Rennes - UMR 6226, Université de Rennes 1, 35042 Rennes Cedex, France

The first example of ligand protected Cu/Zn clusters is described. Reaction of $[CpCu(CN^{t}Bu)]$ with $[Zn_2Cp^{*}_2]$ yields $[(CuCN^{t}Bu)_4(ZnCp^{*})_4]$ (1a) and $[CuCN^{t}Bu)_4(ZnCp^{*})_3(ZnCp)]$ (1b). According to DFT calculations, the $[Cu_4Zn_4]$ unit fulfils the unified superatom model for cluster valence shell closing.

Brass (Cu/Zn) is one of the longest known and most common alloys and a classic example of a Hume Rothery phase. It is used in various applications, due to its increased heat transfer, strength, hardness and corrosion resistance compared to pure copper. Quite in contrast to many other important alloys and intermetallic compounds, the bottom-up nano chemistry of brass and the properties of Cu/Zn nanoalloys have not been widely studied.¹ In particular, only very few reports have appeared demonstrating the wet chemical synthesis of Cu/Zn nanoparticles by precursor routes.²⁻⁵ For example, co-hydrogenolysis of [CpCu(PMe₃)] and [ZnCp*₂] has been found as a pathway to surfactant stabilized brass nano-particles (Cp = C_5H_5 ; Cp* = C_5Me_5 ; Me = CH₃).³ Molecular congeners of nano-brass, i.e. clusters with an atom-precise mixed metal core Cu_aZn_b have not been reported to date. Actually, there is even not single example of a structurally characterized molecular compound in the literature which structure features an unsupported covalent Cu-Zn bond.⁶ For many years we have been working to develop strategies for the controlled synthesis of ligand protected mixed transition metal (A) main group-12/13 metal (B) coordination compounds and/or clusters of the general formula $[A_aB_b]R_c$ (R = hydrocarbon ligand), being inspired by the compositions and structural motifs of Hume Rothery type intermetallics.⁷ We refer to [MoZn₁₂]R₁₂ and $[Pd_2Zn_6Ga_2]R_8$ (R = Cp* and Me) as just two important examples which were obtained by transmetallation reactions using $[Mo(GaCp^*)_6]$ or $[Pd_2(GaCp^*)_5]$ and $ZnMe_2$ as reagents (Ga/Zn and Cp*/Me exchange).^{8,9} However, this strategy failed when applied to the Cu–Zn target. Alternatively, we found "Carmonas compound" $[Zn_2Cp_2^*]$ to be a very flexible reagent for controlled A–Zn bond formation.¹⁰

Herein we report on the synthesis and characterization of the first example of a atom-precise molecular Cu/Zn cluster: two closely related species, namely $[(CuCN^tBu)_4(ZnCp^*)_4]$ (1a) (^tBu = *tert*-butyl) and $[(CuCN^tBu)_4(ZnCp^*)_3ZnCp)]$ (1b) were obtained simultaneously. Treatment of $[CpCuCN^tBu]$ with an *equimolar* amount of $[Zn_2Cp^*_2]$ in toluene at room temperature over a period of 1 h leads to the formation of a dark red solution, from which 1a/1b co-crystallizes as dark red cubes upon cooling at -30 °C (Scheme 1). The crystals 1a/1b have to be manually separated from the pale yellow crystals of the by-product $[Cp^*CuCN^tBu]$, which has been done with the aid of an optical miscroscope in a glovebox under argon. In-situ ¹H NMR indicates the formation of two more byproducts, which are identified as the two zincocene complexes $[ZnCp^*_2]$ and $[ZnCp^*Cp]$. All attempts to separate 1a and 1b from these by-products by washing, re-crystallization from various solvents sublimation or column chromatography remained unsuccessful.

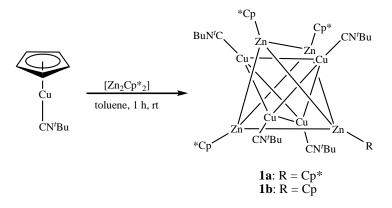

Scheme 1 Formation of the Cu_4Zn_4 clusters [($CuCN^tBu$)₄($ZnCp^*$)₄] (**1a**) and [($CuCN^tBu$)₄($ZnCp^*$)₃(ZnCp)] (**1b**).

The clusters **1a** and **1b** are isostructural and differ only in the nature of one of the four cyclopentadienyl ligands: In 1a all four cyclopentadienly ligands are Cp*, whereas in 1b one of these ligands is Cp. Notably, $[Cp^*CuCN^tBu]$ is not reactive towards $[Zn_2Cp^*_2]$ and the combination of these two compounds did, surprisingly, not lead to the anticipated cluster 1a. Obviously, the reaction of [CpCuCN^tBu] with [Zn₂Cp^{*}₂] involves competitive ligand exchange reactions and is sensitive to ligand variations at the Cu site. The observation of Zn(II) species (ZnR_2 , R = Cp, Cp^*) indicate a formal redox chemical process, where the Zn(I) of $[Zn_2Cp_2^*]$ is oxidized and the Cu(I) of $[CpCuCN^tBu]$ is reduced to Cu(0). Preliminary experiments show that if the reaction is performed in absence of the isonitrile ligand at very low temperature with [Cp*Cu] formed in situ,¹¹ no redox chemistry is observed. Instead, [Zn₂Cp*₂] simply adds to the fragment [Cp*Cu] leading to the triangular, neutral cluster [Zn₂Cu]Cp*₃, which is currently under investigation. The isolated crystals **1a/1b** are stable under an inert gas atmosphere at -30 °C for several weeks, but decompose at room temperature within a few days. The clusters **1a** and **1b** are barely soluble in non polar solvents like *n*-hexane, but readily dissolve in more polar solvents like toluene or benzene. 1a and 1b are stable in solution up to 80 °C, but higher temperatures lead to decomposition of under formation of a metallic precipitate. The ¹H NMR of the red crystals 1a/1b in C_6D_6 at room temperature show a mixture of 1a and 1b in an approximate 1:1 molar ratio (without any further impurities). 1a gives rise to the expected set of signals for a T_d symmetric cluster, *i.e.* one signal at δ = 1.24 ppm (s, 36H) for *tert*-butyl-isonitrile groups and one signal at δ = 2.37 ppm (s, 60H) for the Cp* ligands. In contrast, **1b** shows only C_{3v} symmetry with two signals for the *tert*-butyl-isonitriles (δ = 1.31 ppm (s, 9H), δ = 1.32 ppm (s, 27H)) as well as signals for Cp* (δ = 2.36 ppm (s, 45H)) and Cp (δ = 6.37 ppm (s, 5H)). ¹³C NMR data could not be obtained due the poor solubility of **1a** and **1b**. Liquid injection field desorption ionization mass spectrometry (LIFDI-MS) reveals both $[M]^+$ ion peaks of at m/z [a.u.] = 1389 (1a) and 1319 (1b), together with various fragment peaks due to consecutive loss of organic ligands (see Figure 1 and Figure S4).

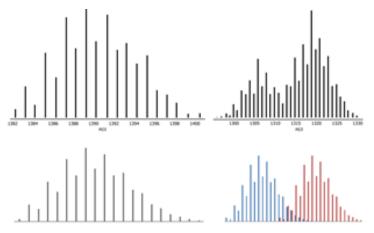


Figure 1. Top left: Molecular ion peak of **1a** (m/z = 1389). Top right: Molecular ion peak of **1b** (m/z = 1319), superimposed with [**1a**-CN^tBu]⁺ (m/z = 1306). Bottom left: Calculated isotopic pattern for [**1a**]⁺. Bottom right: Superimposed calculated isotopic patterns of [**1b**] and [**1a**-CN^tBu]⁺.

The ATR-FTIR spectrum of 1a/1b shows the absorption bands typical of the Cp* units (2937, 2880, 2829 cm⁻¹) and the CN^tBu ligands (2104 cm⁻¹). **1a/1b** crystallizes in the cubic space group $I_{\bar{4}}$ 3m with the molecules of **1a/1b** located on a $\frac{1}{4}$ 3*m* special position. In accordance with the ¹H NMR and LIFDI-MS data, the refinement of the crystal structure was based on a 1:1 solid solution model of 1a and **1b**, i.e. the clusters share the same site in the crystal structure. Clearly, Cu and Zn as neighbouring elements in the periodic cannot be distinguished by routine single-crystal X-ray diffraction experiments. However, according to the T_d symmetry of the cluster found in the ¹H NMR spectrum, only two isomeric forms of 1a and 1b are possible: either with ZnCp*(Cp) and CuCN^tBu coordination or with ZnCN^tBu and CuCp*(Cp). An unambiguous assignment can be made by DFT calculations (see below). It is also possible on the basis of the typical u(CN) stretching vibration in the IR spectrum: This band is observed at 2104 cm⁻¹ for **1a/1b** which is well comparable with the u(CN) stretching vibration found in other CuCNtBu compounds such as the starting compound [CpCuCN^tBu] (2144 cm⁻ ¹).¹² This vibration is very close to that of free CN^tBu (2138 cm⁻¹), while it is shifted to much higher wavenumbers in the few known complexes with a ZnCN^tBu unit (2218-2244 cm⁻¹).¹³ The Cu and Zn content was determined by atomic absorption spectroscopy (calcd. Cu: 18.77, Zn: 19.31 %; found Cu: 19.32, Zn 20.51 %), being in accordance with the assigned 1:1 molar ratio of the two elements. Due to the lack of pure samples of 1a/1b on a multi milligram scale, no CHN analyses have been carried out. The refined structure of **1a/1b** contains residual electron density (1.661 e/Å³) which might be assigned to disordered toluene (see SI for further information).

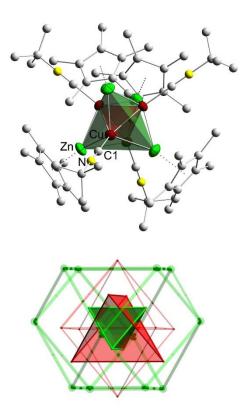


Figure 2 Top: Molecular structure of compound **1a/1b** (red: Cu, green. Zn). Displacement ellipsoids of the metal atoms are drawn at the 30 % probability level. Disordered positions of the Cp* ligands and hydrogen atoms are omitted for clarity. Selected interatomic distances (Å) and angles (°) for **1a/1b**: Cu-Cu 2.471(4), Cu-Zn 2.498(2), Cu-C1 1.892(1), Zn-Cp*_{centroid} 2.055, Cu-Cu-Cu 59.99(1), Cu-Zn-Cu 59.29(11), Zn-Cu-Cu 60.35(5). Bottom: Cu₁₀Zn₁₆ cluster of the γ -brass solid state structure (green: Zn, red: Cu)

The crystallographic site symmetry generates a T_{d} -symmetric arrangement of the four copper atoms, which form the corners of a Cu₄ tetrahedron with Cu–Cu–Cu angles of 60°. The Cu–Cu distances of 2.471(4) Å are longer than the Cu–Cu bond length in $[(IPrCuH)_2]$ (IPr = 1,3-bis(2,6diisopropylphenyl)imidazol-2-ylidene) (2.305(1) Å), which is the shortest Cu-Cu bond known so far, but lie within the range of Cu-Cu distances reported for other molecular compounds (2.305(1) -3.424(2) Å).⁹⁻¹¹ Each face of the Cu₄ tetrahedron is capped by a ZnCp* moiety resulting in a Zn_4 tetrahedron. Both Cu1 and Zn1 occupy a $\frac{1}{4}$ 3m special position in the crystal. To the best of our knowledge 1a/1b are the first molecular compounds containing an unsupported Cu-Zn bond (2.498(2) Å). The only reported complex with a Cu. Zn contact is $[Zn{(p-CH_3CO_2)(salpd-\mu-O,O')Cu}_2]$ (salpd = propane-1,3-diylbis(salicylideneiminate)) with a Cu-Zn distance of 3.038(2) Å, which is clearly a non-boning contact.¹² The bond angles at copper are close to the ideal tetrahedral angle. In the crystal, the Cp/Cp* ligands are severely disordered by symmetry (see SI). The Zn-Cp*_{centroid} / Zn–Cp_{centroid} distances (2.05 Å) are well comparable with the parent compound $[Zn_2Cp_2^*]$ (2.04 Å).¹³ The Cu–C1 distance of 1.89(1) Å) is comparable to the average Cu–CN^tBu distances found in the literature (1.91 Å).⁷ Notably, only one compound exhibiting a Zn–CN^tBu unit with a Zn–C bond length of 2.13 Å was structurally characterized, supporting our Cu/Zn assignment in the structure refinement (vide supra).⁸ Most interestingly, the structural motif of a $[Cu_4Zn_4]$ tetrahedral star is also found in the structure of the famous γ -brass phase Cu₅Zn₈ where an inner Zn₄ tetrahedron is surrounded by an outer Cu₄ tetrahedron, which is the "inverse" metal core to **1a/1b**.¹⁴ The metalmetal distances in y-brass are 2.704(1) Å for the "inner" (Zn₄) tetrahedron and 4.319(1) Å for the

"outer" (Cu₄) tetrahedron with a Cu-Zn distance of 2.611(1) Å, which considerably widened with respect to the to the distances observed in **1a/1b**: 2.462(4) Å for the "inner" (Cu₄) tetrahedron and 4.167(1) Å for the "outer" (Zn₄) tetrahedron with a Cu-Zn distance of 2.493(2) Å.¹⁴ DFT calculations¹⁵ on the two models [(CuCNMe)₄(ZnCp)₄] and [(ZnCNMe)₄(CuCp)₄] (Me for ^tBu and Cp for Cp*; Table S8) confirm the Cu *vs* Zn location assignment, the former being much more stable than the latter (by 2.05 eV). A better agreement with the experimental metal-metal and metal-ligand bond distances, as well as with the u(CN) stretching vibration is also found for [(CuCNMe)₄(ZnCp)₄]. The values of the Cu-Cu and Cu-Zn Wiberg bond indices (0.102 and 0.151 respectively) are consistent with significant covalent bonding within the Cu₄Zn₄ framework. This bonding is largely operated by eight metallic σ -type hybrids of large 4s character which combine into 4 occupied bonding skeletal orbitals and 4 vacant antibonding ones according to the MO interaction diagram shown in Figure S9. The resulting HOMO-LUMO gap (3.57 eV) is large. Thus, there are 4 electron pairs to ensure delocalized bonding along the 16 metal-metal contacts.

In summary, **1a/1b** with the [Cu₄Zn₄] core represent the first example of molecular compounds, containing Cu–Zn bonds. The metal core of the clusters is composed of superimposed Cu₄ and Zn₄ tetrahedra, which represents the "inversed" structure of a structural motif found in γ -brass, Cu₅Zn₈. This swapped Cu and Zn positions is assigned to the preference of the Cp*/CN^tBu binding to Zn and Cu respectively. We suggest rationalizing this composition and structure and its preferred formation with respect to alternatives within the unified superatom concept based on the jellium model for clusters of s/p metals (e.g. coinage metals, closed d¹⁰ sub shell).¹⁶ For a spherical, highly symmetric ligand protected, molecular cluster {[M_m]L_sX_n}^q (q = charge, L = electronically neural weakly coordinating ligand; X = electronegative, electron withdrawing ligand) shell closing is expected for cluster valence electrons cve = 2, 8, 18, 34,...(degenerate jellium states 1S² 1P⁶ 1D¹⁰ 2S² 1F¹⁴, etc.). Regarding Cp* as one electron withdrawing X and CN^tBu as neutral L and taking into account the effective valence 1 for Cu and 2 for Zn the value cve = 8 is obtained for **1a/1b** (1S²1P⁶ shell closing). Thus, **1a/1b** can be described and as ligand protected superatom-like cluster. The tetra capped tetrahedral structure adopted by the Cu₄Zn₄ core is also the most stable structure predicted by the simple Hückel theory for any 8-orbital/8-electron system.

Acknowledgements

This work was funded by the DFG (Fi-502/23-2). K.F. is grateful for a FCI scholarship (https://www.vci.de/fonds) and for the support by the RUB Research School (http://www.research-school.rub.de). We thank the Linden CMS GmbH for support in mass spectrometry.

Notes and references

^a Inorganic Chemistry II, Ruhr-University Bochum, Universitätsstraße 150, 44801 Bochum, Germany. E-mail: roland.fischer@rub.de

^b Institut des Sciences Chimiques de Rennes - UMR 6226 Université de Rennes 1, 35042 Rennes Cedex, France

⁺ Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/b000000x/

 \pm Experimental: To a mixture of 150 mg [CpCuCN^tBu] (0.708 mmol) and 285 mg [Zn₂Cp*₂] (0.708 mmol) 4 ml toluene were added whereas the solution immediately turned dark red. The solution was stirred for a period of one hour at room temperature. The solvent was reduced under reduced pressure and the crude product washed with 2 portions of *n*-hexane (3 ml each). The crude product

was dried in vacuum and 2 ml of toluene were added. Dark red cubic crystals suitable for single crystal X-ray measurements were after storage at -30 °C.

1H NMR (C₆D₆, 25 °C, ppm): δ = 1.24 (36H, CN^tBu (1a)), 1.31 (9H, CN^tBu (1b)), 1.32 (27H, CN^tBu (1b)), 2.36 (45H, C₅Me₅ (1b)), 2.37 (60H, C₅Me₅ (1a)), 6.37 (5H, Cp (1b))

Elemental analysis (%) (C_{57.5}H₉₁N₄Cu₄Zn₄) calcd: Cu 18.77, Zn 19.31 found: Cu 19.32, Zn 20.52

LIFDI-MS: m/z = 1424, 1389, 1319, 1306, 1188, 1170, 1107, 1091, 1040, 1022, 1010, 956, 893, 809, 746, 726, 694 (assignment SI Figure S4)

IR: 2937, 2880, 2829, 2104, 1462, 1415, 1385, 1358, 1249, 1192, 1076, 1006, 853, 790, 744, 723, 690, 582, 545, 501, 461, 442 cm⁻¹

- 1. R. Ferrando, J. Jellinek, R. L. Johnson, Chem. Rev. 2008, 108, 846-910.
- 2. J. Hambrock, M.-K. Schröter, A. Birkner, C. Wöll, R. A. Fischer, Chem. Mater. 2003, 15, 4217-4222.
- 3. M. Cokoja, H. Parala, M. K. Schroeter, A. Birkner, d. B. M. W. E. van, K. V. Klementiev, W. Gruenert and R. A. Fischer, *J. Mater. Chem.*, 2006, **16**, 2420-2428.
- 4. R. E. Cable, R. E Schaak, Chem. Mater. 2007, 19, 4098-4104.
- 5. K. Schütte, H. Meier, C. Gemel, J. Barthel, R. A. Fischer , C. Janiak, Nanoscale, 2014, 6, DOI 10.1039/C3NR05780A.
- 6. T. Bollermann, C. Gemel, R. A. Fischer, Coord. Chem. Rev. 2012, 256, 537–555.
- 7. S. González-Gallardo, T. Bollermann, R. A. Fischer, R. Murugavel, Chem. Rev. 2012, 112, 3136-3170.
- 8. T. Cadenbach, T. Bollermann, C. Gemel, I. Fernandez, M. von Hopffgarten, G. Frenking and R. A. Fischer, *Angew. Chem., Int. Ed.*, 2008, **47**, 9150-9154.
- 9 T. Bollermann, M. Molon, C. Gemel, K. Freitag, R. W. Seidel, M. von Hopffgarten, P. Jerabek, G. Frenking, R. A. Fischer, *Chem. Eur. J.* 2012, **18**, 4909-4915.
- 10. T. Bollermann, K. Freitag, C. Gemel, R. W. Seidel, R. A. Fischer, *Organometallics*, 2011, 30, 4123–4127.
- 11. C. Zybill and G. Mueller, *Organometallics*, 1987, **6**, 2489-2494.
- 12. T. Kruck and C. Terfloth, *Chem. Ber.*, 1993, **126**, 1101-1106.
- 13. M. Bochmann, G. C. Bwembya and A. K. Powell, *Polyhedron*, 1993, **12**, 2929-2932.
- 9. N. P. Mankad, D. S. Laitar and J. P. Sadighi, Organometallics, 2004, 23, 3369-3371.
- 10. Q.-H. Wei, G.-Q. Yin, L.-Y. Zhang, L.-X. Shi, Z.-W. Mao and Z.-N. Chen, *Inorg. Chem.*, 2004, **43**, 3484-3491.
- 11. J. Beck and J. Straehle, *Angewandte Chemie*, 1985, **97**, 419-420.
- 12. C. Fukuhara, K. Tsuneyoshi, N. Matsumoto, S. Kida, M. Mikuriya and M. Mori, *J. Chem. Soc., Dalton Trans.*, 1990, 3473-3479.
- 13. I. Resa, E. Carmona, E. Gutierrez-Puebla and A. Monge, *Science*, 2004, **306**, 411.
- 14. O. Gourdon, D. Gout, D. J. Williams, T. Proffen, S. Hobbs and G. J. Miller, *Inorg. Chem.*, 2007, **46**, 251-260.
- 15. PBE0/Def2-TZVP level. Details of the calculations are provided in the SI.
- 16. H. Hakkinen, Chem. Soc. Rev., 2008, 37, 1847-1859.