



HAL
open science

Recent achievements on inorganic electrode materials for lithium-ion batteries.

Laurence Croguennec, M Rosa Palacin

► **To cite this version:**

Laurence Croguennec, M Rosa Palacin. Recent achievements on inorganic electrode materials for lithium-ion batteries.. *Journal of the American Chemical Society*, 2015, 137 (9), pp.3140-3156. 10.1021/ja507828x . hal-01139982

HAL Id: hal-01139982

<https://hal.science/hal-01139982v1>

Submitted on 1 Feb 2021

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Perspective

Recent achievements on inorganic electrode materials for lithium ion batteries

Laurence Croguennec, and M. Rosa Palacin

J. Am. Chem. Soc., **Just Accepted Manuscript** • DOI: 10.1021/ja507828x • Publication Date (Web): 13 Feb 2015

Downloaded from <http://pubs.acs.org> on February 16, 2015

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

Recent achievements on inorganic electrode materials for lithium ion batteries

Laurence Croguennec,^{†,‡,#} M. Rosa Palacin^{§,‡,*}

[§] Institut de Ciència de Materials de Barcelona, ICMA-B-CSIC, Campus de la UAB, 08193 Bellaterra, Catalonia (SPAIN).

[†] CNRS, Univ. Bordeaux, ICMCB, UPR 9048, 33600 Pessac (FRANCE).

[‡]ALISTORE-ERI European Research Institute.

[#] RS2E, Réseau Français sur le Stockage Electrochimique de l'Energie, FR CNRS#3459 (FRANCE)

* Corresponding author: rosa.palacin@icmab.es

ABSTRACT:

The origin of the lithium-ion battery technology is rooted in the studies of intercalation of guest ions into inorganic host materials developed ca. 40 years ago and further turned into a commercial product which will soon blow its 25th candle. Intense research efforts during this time have resulted in the development of a large spectrum of electrode materials together with deep understanding of the underlying structure-property relationships that govern their performance. This has enabled an ever increasing electrochemical yield together with the diversification of the technology into several sub-families, tailoring materials to application requirements. The present paper aims at providing a global and critical perspective on inorganic electrode materials for lithium ion batteries categorized by their reaction mechanism and structural dimensionality. Specific emphasis is put on recent research in the field, which beyond the chemistry and microstructure of the materials themselves also involves considering interfacial chemistry concepts alongside progress in characterization techniques. Finally a short personal perspective is provided on some plausible development of the field.

KEYWORDS: lithium batteries, electrode materials, insertion, alloying, conversion

1. INTRODUCTION

Lithium ion batteries entered the market in the 1990's and are currently a very well established and familiar commercial product. Its development parallel to the boost of the consumer electronic market is a striking example of synergistic application driven product development with continuous research resulting in incremental performance improvement. In addition to that, recent concerns to decrease societal dependence on fossil fuels through electrification of transportation are opening a new market for this technology, involving larger scale storage and hence a somewhat different set of requirements. Last but not least, the imperious need to implement electrical energy storage in the grid to ensure reliability of supply while enhancing renewable penetration has brought about a re-evaluation of the energy storage technologies available to these even larger scale applications. In spite of some concerns related to cost and lithium risk supply, the potential of Li-ion technology for such a purpose has been identified and several demonstration projects are currently on going worldwide.

The above discussed strategic trends have prompted massive and intense research efforts to improve batteries in terms of energy and power density, safety, cycle life, cost, environmental aspects etc. Indeed, requirements for transport applications are specially challenging as enhanced safety is mandatory and energy density determines the vehicle autonomy range. Such efforts (e.g. almost 6000 records published in 2013 related to Li-ion technology) emerge both from the industrial and academic research communities, the strong interaction between them deserving special mention.

In a historical perspective, the study of intercalation reactions by the inorganic solid state chemistry community¹ turned out to be a cornerstone in the battery development. Indeed, the potential of suitable host compounds to allow reversible (usually topotactic) insertion and deinsertion of lithium ions, without major structural changes while exhibiting suitable redox chemistry thanks to the presence of transition metals, was soon realized. The initial prospects of building extremely high energy density secondary cells using lithium metal anodes and conventional organic solvent based electrolytes had to be soon dismissed due to issues related to non-uniform lithium plating (unsurprising when considering classical electroplating notions) which resulted in unacceptable safety risks. Lithium based alloys appeared as the first natural solution to replace lithium metal, but proved unsuccessful due to the large volume changes involved in the electrochemical alloying-dealloying processes, which ultimately resulted in severe capacity fading upon cycling. The bottleneck for commercialization was overcome returning to square one concepts by selecting a negative electrode (low potential) material also operating through an intercalation redox mechanism. Following this approach, the use of substantially different materials to those proposed for the positive electrode (high potential) was compulsory to enable cell operation potentials outperforming those of aqueous electrolyte nickel and lead based cells which were state-of-the art technologies at the time. Thus, early lithium ion batteries consisted of LiCoO₂ and graphite at the positive and negative electrode, respectively. After 25 years of development the concept remains the same, but the spectrum of materials used in commercial cells has widened to the extent that several large families of lithium ion technologies exist.

1
2
3 In practical lithium-ion batteries the electrodes are conventionally tape casted on a metal
4 current collector (aluminum for the positive and copper for the negative) and aside the active
5 materials contain additives to enhance electronic conductivity (typically carbon black) and a
6 binder (e.g. polyvinylidene fluoride, PVDF) to improve adhesion, mechanical strength and ease
7 of processing. Positive and negative electrodes are separated by a microporous film (such as
8 polyethylene or polypropylene) and the whole assembly is impregnated with the electrolyte.
9 The electrolyte solvents commonly used (mixtures of different alkyl carbonates) are in fact
10 unstable below ca. 0.8V vs. Li⁺/Li and above ca. 4.5V vs. Li⁺/Li in presence of electrode
11 materials, which depending on their state of charge/discharge can be strongly
12 oxidizing/reducing.² Degradation reactions do often involve also the electrolyte salt (usually
13 LiPF₆) and water traces, which can result in formation of HF and lead to transition metal
14 dissolution. The resulting insoluble products, however, form a solid passivation layer (the Solid
15 Electrolyte Interphase, SEI) at the surface of the negative electrode.^{3,4,5} An interphase is also
16 formed at the surface of the positive electrode, sometimes denoted the Surface Layer (SL).
17 Thus, the use of present electrolytes during cell operation is entirely made possible through
18 proper chemical passivation of electrode surfaces.
19
20
21
22

23
24 Since the operation principle of the Li-ion technology together with its evolution were already
25 discussed in a recent perspective paper in this journal,⁶ the present paper focuses on key
26 recent advances and identification of existing bottlenecks in the field. As the global aim is to
27 inspire future research to overcome existing challenges which will certainly benefit from a
28 diversity of perspectives coming from different backgrounds and scientific domains, special
29 effort has been taken to direct the text to the non-specialised readership hoping that this will
30 serve as a springboard for further reading.
31
32
33
34

35 2. INSERTION ELECTRODES

36
37 As mentioned above, current commercial lithium ion batteries use electrode materials
38 exhibiting an insertion redox reaction mechanism for both the positive and negative
39 electrodes, which results in electrochemical capacities limited to one electron per transition
40 metal. Such materials can be classified according to the dimensionality of their structural
41 framework (3D or 2D). Nonetheless, it has to be highlighted that this is not necessarily related
42 to the diffusion pathways of lithium ions in the structure. For instance, LiMn₂O₄ and LiFePO₄
43 are both hosts exhibiting a 3D structure with the lithium diffusion being 3D in the former, but
44 only 1D in the latter⁷. Most of the materials developed exhibit high insertion potentials and are
45 thus suitable for use as positive electrode materials. The spectrum of insertion negative
46 electrode materials is much more limited owing to (i) the very good performance of graphitic
47 materials, which prompted only limited research efforts as compared to those devoted to the
48 positive counterparts and (ii) the need of low operation potentials, which limits the choice of
49 redox centers available.
50
51
52
53

54 The next sections are devoted to the discussion of recent research achievements in the field of
55 insertion electrode materials, both 2D (graphite and layered oxides) and 3D (spinel and
56 polyanionic).
57
58
59
60

2.1. 2D STRUCTURES

Most types of carbon react with lithium ions at low potential ($\sim 0.1-1$ V vs. Li^+/Li) and are thus suitable for use as negative electrode materials. The amount of lithium reversibly incorporated in the carbon lattice (the reversible capacity), the faradaic losses during the first cycle (the irreversible capacity) and the profile of the potential composition profile can exhibit important differences.⁸ Indeed, the redox process is strongly influenced by macro- and micro-structural features including the specific surface, surface chemistry,⁹ morphology, crystallinity and orientation of the crystallites.¹⁰ Hard carbons can deliver high capacity since the random alignment of small-dimensional graphene layers provides significant porosity able to accommodate lithium,¹¹ yet with an irreversible capacity higher than that of graphite. Their rate capability (power performance) is also usually limited as their volumetric capacity penalized by a lower density. The generalized use of graphite electrodes in commercial batteries was enabled by the development of ethylene carbonate (EC) based electrolytes, which form an effective SEI that prevents exfoliation¹² due to solvent co-intercalation. Its full reduction involves the formation of LiC_6 (with 372 mAh/g and 975 mAh/cm³ gravimetric and volumetric capacity respectively).

On the positive side, the layered oxide LiCoO_2 (Figure 1) remains widely used as positive electrode in Lithium-ion batteries for portable devices, as it delivers attractive volumetric energy density, excellent cyclability and high rate capability. The main caveat of this compound is its low reversible capacity; equivalent to the exchange of a mere 0.5 Li^+ ions per mol of Co and thereby limited to ca 150 mAh/g, even if surface modifications have allowed increasing the upper voltage limit of operation and thus the reversible capacity, with the exchange of up to 0.7 Li^+ per Co.¹³ The microstructure of the material itself is also in constant evolution in order to increase the tap density and the volumetric energy density. Nevertheless, its use in large-format batteries is prevented by its high cost and limited thermal stability of the oxidized $\text{Li}_{1-x}\text{CoO}_2$ phase which may create safety concerns. This feature is common to all layered $\text{Li}_{1-x}\text{MO}_2$ for $x < 1/2$ with oxygen being released from the lattice and reacting with the electrolyte solvents through exothermic reactions. Reduction of the transition metal ions occurs together with migration of ca. 25% of the transition metal ions from the metal layer to the lithium interlayer through empty tetrahedral sites (Figure 2) causing a structural transformation from layered 2D to spinel 3D with the oxygen lattice remaining unaffected (AB CA BC packing with A, B and C being the three positions of a triangular lattice).

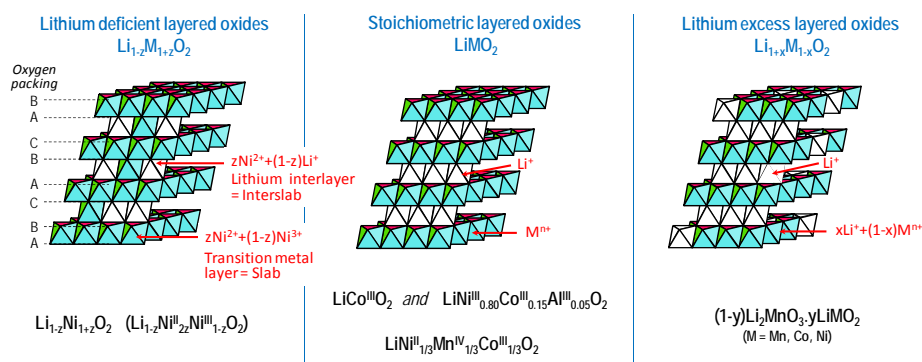


Figure 1: Scheme depicting the crystal structure of layered Li-M-O oxides with different compositions and cation distributions.

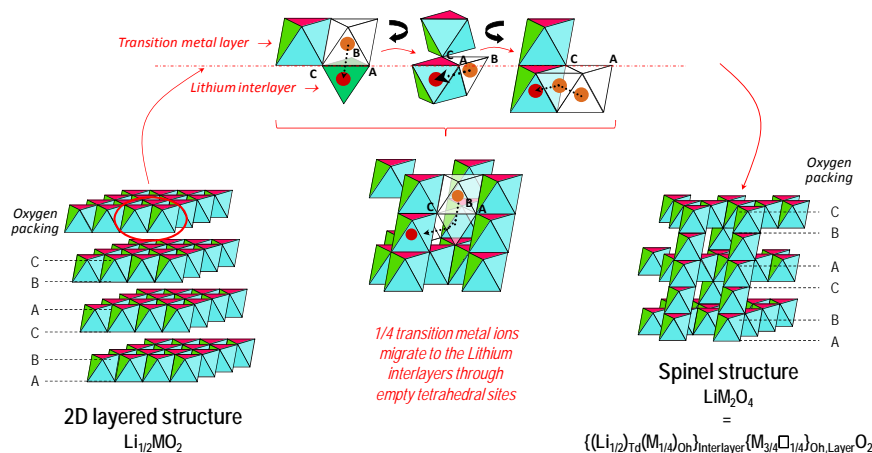


Figure 2: Scheme depicting the pathway for layered to spinel structural transition observed for deintercalated layered oxides Li_xMO_2 at high temperature (Td and Oh, for tetrahedral and octahedral sites respectively). Note that for the sake of simplicity lithium ions are not represented. Adapted with permission from¹⁴ (Guilmard, M.; Croguennec, L.; Denux, D.; Delmas, C. *Chem. Mater.* **2003**, *15*, 4476). Copyright (2003) American Chemical Society.

$\text{LiNi}^{\text{III}}\text{O}_2$, isostructural to LiCoO_2 , was early considered as a possible lower cost alternative, but its synthesis as a pure stoichiometric 2D compound is difficult to achieve. Indeed, $\text{Li}_{1-z}\text{Ni}_{1+z}\text{O}_2$ ($z > 0$) is most commonly obtained, with the presence of extra nickel ions in the interlayer lithium sites (Figure 1) and is thus, as such, of limited interest. Partial cobalt and aluminum substitutions for nickel were shown to be the key to control the 2D character of the structure,¹⁵ bringing also enhanced thermal stability, the optimum composition being $\text{LiNi}^{\text{III}}_{0.80}\text{Co}^{\text{III}}_{0.15}\text{Al}^{\text{III}}_{0.05}\text{O}_2$ (NCA, reversible capacity of 185 mAh/g involving mainly the $\text{Ni}^{3+}/\text{Ni}^{4+}$ redox couple at an average voltage of 3.7 V vs. Li^+/Li (Figure 1)). $\text{LiNi}^{\text{II}}_{1/3}\text{Mn}^{\text{IV}}_{1/3}\text{Co}^{\text{III}}_{1/3}\text{O}_2$ (NMC) exhibits an even higher thermal stability in the delithiated state, due to the stabilization effect of the tetravalent manganese ions^{16,17} and even if the manganese ions do not participate in the redox processes this compound exhibits an attractive reversible capacity of 170 mAh/g at an average voltage of 3.7 V vs. Li^+/Li . Such improvements paved the way for the commercial use of NCA and NMC in larger cells for transport applications, even if they remain expensive due to the cost of both nickel and cobalt. NCA is more attractive for high rate applications due to its higher electronic and ionic conductivities (electron hopping among nickel ions promotes faster lithium diffusion within the structure), as ordering of the Ni, Mn and Co ions in NMC is detrimental to electron mobility (Figure 1).

An attractive strategy which in our opinion deserves to be widely explored has been reported in the last few years by Y.K. Sun et al. to further optimize the energy density and thermal stability of Ni-rich layered oxides by developing core-shell or full gradient composition materials.^{18,19} For instance, $\text{LiNi}_{0.80}\text{Co}_{0.10}\text{Mn}_{0.10}\text{O}_2$ at the core provides high capacity, while $\text{LiNi}^{\text{II}}_{1/2}\text{Mn}^{\text{IV}}_{1/2}\text{O}_2$ at the surface ensures high thermal stability. While difficulties may be encountered to prepare an homogeneous material at large scale, fine control of the process parameters (pH, pumping rates of the precursors, stirring conditions ...) is certainly the path to success.

The family of layered materials currently attracting most interest is that of Li- and Mn-rich layered oxides (commonly denoted $(1-y)\text{Li}_2\text{MnO}_3.y\text{LiMO}_2$ ($\text{M} = \text{Mn, Co, Ni}$), with the overall Li/M ratio >1) (Figure 1) which exhibit very high energy densities at an affordable cost.^{20,21,22}

They have been described alternatively either as composites.^{20,23,24,25} or “solid solutions”^{26,27,28,29,30,31} between $\text{Li}_2\text{Mn}^{\text{IV}}\text{O}_3$ and layered $\text{LiM}^{\text{III}}\text{O}_2$ with, in both cases, a certain degree of cation (Li, M, Mn) ordering within the transition metal layers. The control of the composition and structural features of these materials is tricky as revealed by all the apparent discrepancies reported, with the oxygen partial pressure and the thermal history (intermediate treatment at low temperature, heating and cooling rates ...) being critical synthesis parameters to prevent phase separation.^{32,33,34,35,36}, while a rigorous control of the stoichiometry (a ratio close to 1:2 between the larger and the smaller cations) and oxidation state of each transition metal are crucial to achieve extended cation ordering.³⁷ The control of the composition and local structure enable tuning the formation of a 3D percolating vacancy pathway for fast lithium diffusion in these 2D structures and yielding thereby optimized electrochemical capacity and rate capability: $x = 1.09$ is found to be the percolation threshold for $\text{Li}_x\text{M}_2-x\text{O}_2$ (whatever their structure: layered, spinel, disordered or rock-salt), while $x > 1.22$ allows to reach a reversible capacity of 1 Li^+ per transition metal.³⁸

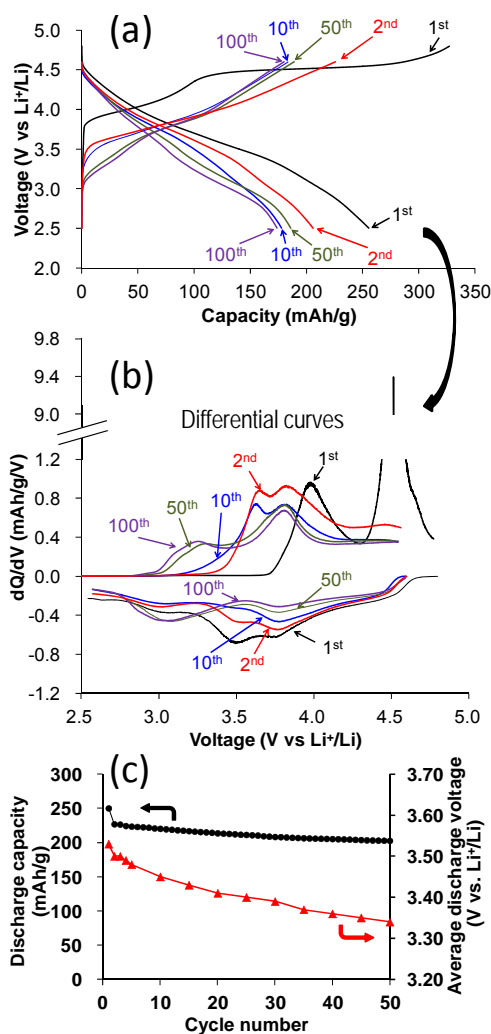


Figure 3: Comparison of charge and discharge curves obtained for $\text{Li}/\text{Li}_{1.20}\text{Ni}_{0.13}\text{Mn}_{0.54}\text{Co}_{0.13}\text{O}_2$ cells for different cycle numbers (a) and the corresponding differential curves $dQ/dV = f(V)$ (b). Changes in the discharge capacity and in the average discharge voltage versus the cycle number (c). Adapted from ⁴⁶ *J. Power Sources* **2013**, 236, 250. Koga, H.; Croguennec, L.; Ménétrier, M.; Mannesiez, P.; Weill, F.; Delmas, C. « Different oxygen redox participation for bulk and surface : A possible global explanation for the cycling mechanism of $\text{Li}_{1.20}\text{Mn}_{0.54}\text{Co}_{0.13}\text{Ni}_{0.13}\text{O}_2$ ». Copyright (2013), with permission from Elsevier.

1
2
3 A common feature for all Li-rich layered oxides is a long (i.e. high capacity) “plateau”, observed
4 only at the end of the first oxidation (Figure 3), once all the transition metal ions have already
5 reached the tetravalent state. Lu et al. proposed that the charge compensation mechanism for
6 lithium ion deintercalation was oxygen loss³⁹ but even if confirmed by in situ differential
7 electrochemical mass spectrometry (DEMS),⁴⁰ its amount was shown to be too low to
8 counterbalance all the lithium ions deintercalated during the “plateau”. The observed behavior
9 can only be explained through the reversible participation of oxygen anions in the redox
10 processes thanks to hybridization between their *p* levels and the *d* levels of the transition
11 metal,^{41,42,43} which increases with enhancing electronegativity and oxidation state (Figure 4).
12 This reaction is reversible within the bulk, occurring without any major structural modification,
13 while at the surface oxidized oxygen ions are destabilized and lost causing structural
14 reorganization and transition metal migration with concomitant formation of “dense” layered-
15 type or defective domains commonly denoted “splayed” (i.e. intermediate between layered
16 and spinel)^{44,45,46,47} (Figure 3). The kinetics of the surface modification and thus the fraction of
17 “splayed” structure formed depend not only on the powder specific surface area,⁴⁶ but also
18 on the composition.⁴⁸ Indeed, the intrinsic stability of each transition metal M^{n+} in the
19 intermediate tetrahedral sites in the pathways for diffusion/migration (Figure 2) governs the
20 destabilization of oxidized oxygen ions and thus the degree of structural reorganization.

21
22 While it is clear that the largest advantage of Li-rich layered oxides lies in their outstanding
23 capacities (>230 mAh/g), they suffer from a continuous voltage decay upon cycling which is the
24 main handicap to their practical implementation (Figure 3).^{49,50,51} It is induced by the
25 irreversible structural modifications occurring at the outer part of the particles (that determine
26 the potential measured). Using $\text{Li}_2\text{Ru}_{1-y}\text{Sn}_y\text{O}_3$ as a model compound, for which oxygen anions
27 participate in the redox process with neither oxygen loss nor migration of transition metal
28 ions, Sathiya et al. elegantly demonstrated that it is possible to tailor the composition of
29 layered oxides to achieve high voltages with large reversible capacity and low fading with no
30 voltage decay.⁴⁸ The proof of concept being demonstrated, the challenge is now to develop
31 alternative compounds containing low cost and environmentally friendly metals as
32 electronegative as possible, to promote the participation of oxygen anions in the redox
33 processes and hence larger reversible capacities. Thus, tailoring of the composition is an
34 imperious track to follow to stabilize these Li-rich layered oxides for commercial viability. The
35 transition metals of choice must be unstable in tetrahedral sites to avoid migration and thus
36 prevent structural reorganization and voltage hysteresis. An alternative interesting approach
37 to block or at least delay the structural reorganization is partial substitution by cations that do
38 not participate to the redox processes and are stable in tetrahedral sites.⁵²

39
40 Knowing that the redox processes in these compounds involve oxygen anions with the
41 exchange of a larger number of electrons per transition metal, compositions with heavier
42 transition metals such as 4d elements now become attractive. Therefore, a large panel of
43 compositions can be designed with the formulae $\text{Li}_4\text{MM}'\text{O}_6$ (MM' being $M^{\text{II}}M^{\text{VI}}$, $M^{\text{III}}M^{\text{V}}$ or
44 $M^{\text{IV}}M^{\text{IV}}$)⁵³ and Li_3MRuO_5 (MRu = $\text{Co}^{\text{III}}\text{Ru}^{\text{IV}}$ or $\text{Ni}^{\text{II}}\text{Ru}^{\text{V}}$ which could be expressed as
45 $0.5\text{Li}_2\text{RuO}_3 \cdot 0.5\text{LiMO}_2$ or as $\text{Li}[\text{Li}_x\text{M}_{1-3x}\text{Ru}_{2x}]\text{O}_2$ with $x = 0.2$) which are well worth exploring.⁵⁴

46
47
48
49
50
51
52
53
54
55
56
57 The findings reported above clearly illustrate that in order to achieve attractive reversible
58 capacities, the oxidation (charge) should proceed to high voltages (> 4.6 V vs. Li^+/Li , Figure 3),
59

i.e. at the limit of the stability of the currently used electrolytes. Thus, interfacial chemistry offers an interesting research playground as surface properties have a direct impact on the irreversible capacity and rate capability. Approaches based on the formation of coated, core-shell or concentration gradient architectures have proved to be effective to modify the surface chemistry and thus its reactivity.^{55,56,57} Well beyond the stabilization of the active material versus transition metal dissolution and electrolyte degradation, we think that the formation of these complex architectures could also promote stabilization of the surface versus oxygen loss and subsequent transition metal rearrangement at the outer part of the particles.

In our opinion the road is still long and winding before the lithium-excess layered oxides may reach the application level. Nevertheless, the recent results indicate feasibility. Furthermore, the reversible participation of oxygen anions in the redox mechanism and the possibility of lithium ion diffusion through a 3D channel of percolating vacancies, even in disordered structures, provide exciting perspectives for the development of new high capacity and high energy density insertion positive electrode materials.

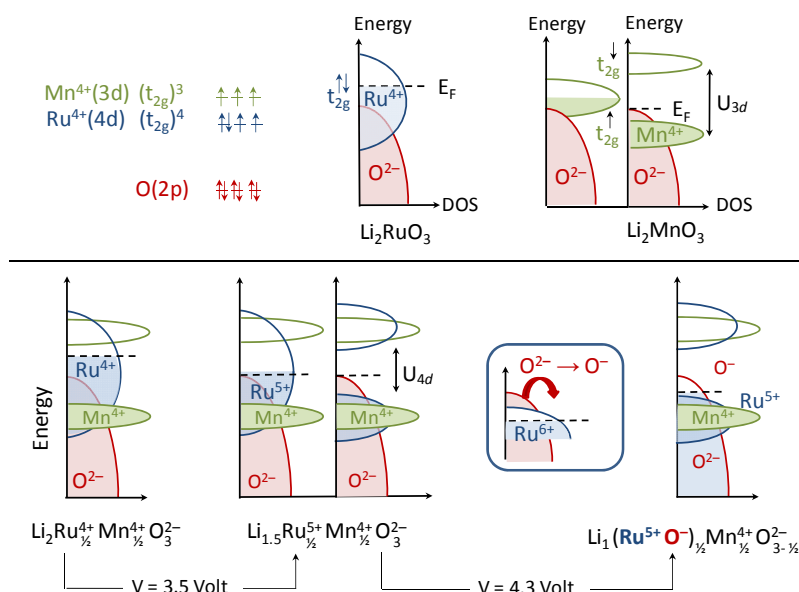


Figure 4. Schematic representations of the density of states (DOS) of Li_2RuO_3 , Li_2MnO_3 and $Li_{2-x}Ru_{1/2}Mn_{1/2}O_3$ in which the Fermi level (E_F) is represented by a horizontal dotted line. This figure illustrates the more electronegative character of Ru compared to Mn, the stronger $Ru(4d) - O(2p)$ hybridization compared to $Mn(3d) - O(2p)$ and the electronic levels involved in the redox processes, i.e. the $Ru^{4+}(t_{2g})$ band from $x = 2$ to 1.5 and the $O(2p)$ from $x = 1.5$ to 1.0. Reprinted with permission from⁴² (Sathiyaraj, M.; Ramesha, K.; Rousse, G.; Foix, D.; Gonbeau, D.; Prakash, A. S.; Doublet, M. L.; Hemalatha, K.; Tarascon, J.-M. *Chem. Mater.* **2013**, *25*, 1121). Copyright (2013) American Chemical Society.

2.2. 3D STRUCTURES

2.2.1 Spinel frameworks

The 3D negative electrode materials so far studied are mainly based on the Ti^{4+}/Ti^{3+} redox couple⁵⁸ and exhibit insertion potentials between 1.5 and 2 V vs. Li^+/Li . Such high potentials induce a severe penalty in the energy density as compared to carbonaceous anodes, but bring

1
2
3 enhanced safety.⁵⁹ Indeed, at these potentials the electrolyte is stable and no SEI formation is
4 *a priori* expected. Furthermore, the risk of lithium metal deposition at high current (fast
5 charging) is suppressed. From a more technological point-of-view, such materials enable the
6 use of aluminum current collectors at the negative electrode (which would form alloys with
7 lithium at low potential using graphite) replacing the heavy and expensive copper. The
8 different TiO₂ polymorphs, also well investigated for a myriad of other applications have
9 received significant attention.^{60,61} Yet, they do exhibit somewhat too high operation potentials
10 for a negative electrode and Li₄Ti₅O₁₂ is the only titanium based compound having reached the
11 commercial stage. It exhibits a defect spinel structure that can be described as
12 [Li]_{8a}[Li_{1/3}Ti_{5/3}]_{16d}[O₄]_{32e} and intercalates three lithium ions per formula unit (175 mAh/g) at 1.55
13 V vs. Li⁺/Li to form Li₇Ti₅O₁₂ with almost no changes in the lattice volume,⁶² being thus termed
14 “zero strain material”. This fact has made possible the fundamental study of nano-size effects
15 in absence of strains and interface energy, which is uncommon for electrode materials.⁶³ As
16 Li₄Ti₅O₁₂ is electronically insulating, intense efforts have been devoted to increase its
17 conductivity through doping or coating approaches, and hereby adequate performance at high
18 charge/discharge rates (rate capability) has been widely reported. The insulating character of
19 pristine Li₄Ti₅O₁₂ is thus by no means a bottleneck for application, especially since during the
20 early stages of lithium intercalation and titanium reduction formation and rapid propagation of
21 percolating electronically conductive pathways takes place.^{64,65} The practical use of titanium
22 oxides in general is currently being challenged by concerns raised about their presumed
23 stability towards the electrolyte^{66,67,68} based on observation of gas evolution^{69,70} which was
24 attributed to catalytic effects. However, recent reports attribute such phenomena to water
25 impurities in the electrolyte⁷¹ and thus the controversy is not yet solved.

26
27
28
29
30
31
32 LiMn₂O₄, also exhibiting spinel structure is an attractive alternative to LiCoO₂,^{72,73} owing to the
33 low cost, wider abundance and low toxicity of manganese. It delivers a reversible capacity of
34 110 mAh/g at a potential around 4 V vs. Li⁺/Li. Nevertheless, it was rapidly shown to suffer
35 from severe capacity fading at high temperatures related to dissolution of manganese, as Mn²⁺
36 species formed through disproportionation (2Mn³⁺ → Mn²⁺ + Mn⁴⁺) or acid leaching of
37 Li_{1-x}Mn₂O₄ by HF arising from reaction of water impurities with the electrolyte salt. Different
38 routes have been considered to stabilize LiMn₂O₄: (i) partial cationic or anionic substitution (Ni,
39 Al, F ...) or (ii) surface modifications through the formation of a coating or the use of additives
40 in the electrolyte, with overall only limited success.¹³

41
42
43
44 Another spinel compound which has captured researchers' attention is LiNi^{II}_{0.5}Mn^{IV}_{1.5}O₄.^{74,75} It
45 exhibits a high operating voltage (4.7 V vs. Li⁺/Li r), which challenges conventional electrolyte
46 stability, involving the Ni²⁺/Ni³⁺ and Ni³⁺/Ni⁴⁺ couples with the exchange of 0.5 Li⁺ per
47 transition metal (i.e. a reversible capacity of 135 mAh/g). Depending on the synthesis
48 conditions, LiNi_{0.5}Mn_{1.5}O₄ can crystallize in two space groups; *P4₃32* and *Fd3m*, the transition
49 metal ions Ni and Mn being ordered in two octahedral sites for the former and randomly
50 distributed for the latter. The disordered spinel is typically obtained at 900°C, often with Li_xNi_{1-x}
51 O impurities, although Patoux et al. have shown that a disordered phase with composition
52 LiNi_{0.4}Mn_{1.6}O₄ can be achieved pure.⁷⁶ The disordered phase exhibits lower capacity fading and
53 higher rate capability, which has been related to its better electronic and ionic conductivities
54 (Figure 5). Indeed, electrons delocalization occurs among manganese (Mn³⁺ and Mn⁴⁺) and
55 nickel (Ni²⁺, Ni³⁺ and Ni⁴⁺), whereas in the ordered phase LiNi^{II}_{0.5}Mn^{IV}_{1.5}O₄, the Ni²⁺ ions are

isolated and surrounded by six non active Mn^{4+} ions, preventing any mobility of the electrons. Mn dissolution is also less severe for the high voltage spinel $\text{LiNi}_x\text{Mn}_{2-x}\text{O}_4$ than for LiMn_2O_4 , as the content of Mn^{3+} ions in the spinel structure is minimized. Despite significant improvements, good performance in full cells needs to be fully confirmed, especially if involving storage at high potential and/or moderate temperature operation (Figure 5).

As in the case of some of the Li-rich materials discussed in the previous section one of the crucial issues for practical application is the absence of electrolytes compatible with operation at such high potentials. While results reported with electrolytes based in fluorinated carbonates and ethers, which oxidize at higher potentials and temperatures, are promising,^{77,78,79} additives such as succinic and glutaric anhydrides have been proved to help in forming effective SL that behaves as polymer electrolyte⁸⁰ and thus may pave the way to success.

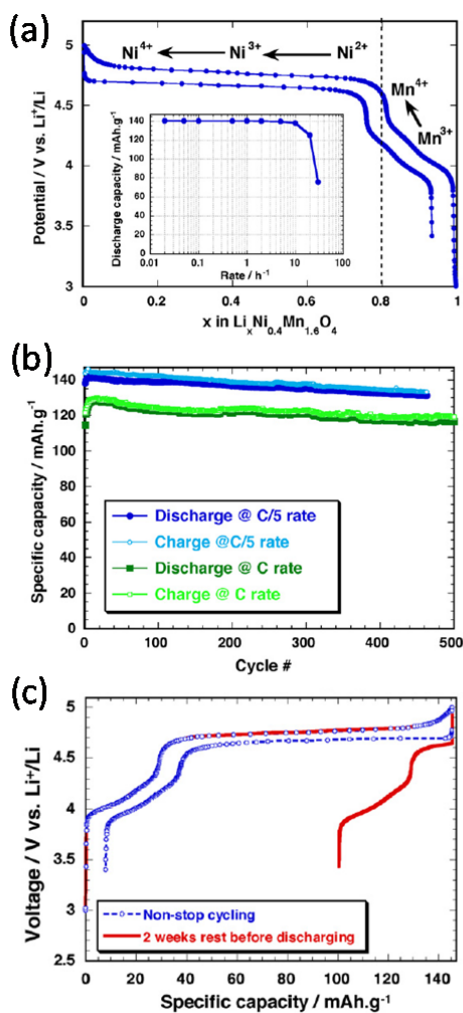


Figure 5: (a) Potential-composition profile of the non-stoichiometric and non-ordered $\text{LiNi}_{0.4}\text{Mn}_{1.6}\text{O}_4$ spinel oxide vs. lithium at C/5 rate and at 20°C: the specific capacity vs. discharge rate is given in inset. The small amount of Mn^{3+} ions is first oxidized to Mn^{4+} and then, Ni^{2+} ions are oxidized to Ni^{3+} and Ni^{4+} . (b) Specific capacity vs. cycle number obtained at C and C/5 rates at 20°C. (c) Illustration of the effect of a two weeks storage at high voltage, cycling was performed at C/5 at 20°C. Adapted from⁷⁶ *J. Power Sources* **2009**, *189*, 344. Patoux, S. ; Daniel, L. ; Bourbon, C. ; Lignier, H. ; Pagano, C. ; Le Cras, F. ; Jouanneau, S. ; Martinet, S. « High voltage spinel oxides for Li-ion batteries : From the material research to the application ». Copyright (2009), with permission from Elsevier.

2.2.2 Polyanionic frameworks

Since the demonstration by Padhi et al. that lithium ions can be extracted reversibly from olivine LiFePO_4 at ca. 3.5 V vs. Li^+/Li (two-phase mechanism involving a Li-poor Li_xFePO_4 phase and a Li-rich $\text{Li}_{1-x}\text{FePO}_4$ phase),⁸¹ this positive electrode material has received considerable attention from the scientific community which has ultimately led to commercialization and is widely described in recent reviews.^{63,82,83} One of the main breakthroughs in this path lies in the formation of a thin conductive carbon coating at the surface of LiFePO_4 nanoparticles⁸⁴ as a means to enhance electronic conductivity. After that seminal work, innumerable studies focused on different aspects and, through a pathway involving large controversies, finally brought in-depth understanding of the behaviour of this compound upon cycling and of its redox mechanism: Particle size has a strong effects in the electrochemical signature of LiFePO_4 which can be rationalized in terms of interface energy (mainly associated to the strains induced by volume changes in volume at the two-phase reaction front). Thus, smaller size involves a reduction of the two-phase domain during operation^{85,86,87,88} and a slightly higher operation potential.^{89,90} In the extreme case of a sample consisting of a wide size distribution of nanoparticles, the potential profile is not anymore a flat plateau but a sloping curve, the latter not being the signature of a solid solution reaction, but rather of a series of different size particles enduring a two phase process.

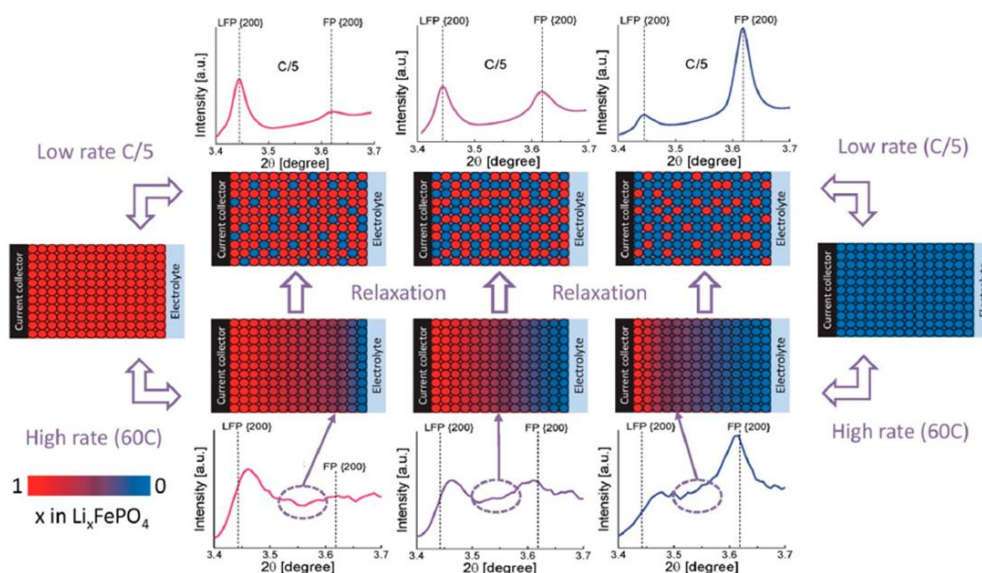


Figure 6: Model proposed by Zhang et al. to describe the phase distribution in LiFePO_4 electrodes at high and low rates or at open circuit. At low rates the electrode is near equilibrium, and no significant effect due to Li-concentration and polarization exists. As a consequence, the phase transition occurs randomly throughout the electrode, and only the two end member phases Li-poor Li_xFePO_4 and Li-rich $\text{Li}_{1-x}\text{FePO}_4$ are observed. At high rates the polarization induces, depending on the particle size and electronic conductivity within the electrode, a potential gradient and a distribution of solid-solution compositions within and between the particles. Reprinted with permission from⁹³ (Zhang, X.; van Hulzen, M.; Singh, D.P.; Brownrigg, A.; Wright, J.P.; van Dijk, N.H.; Wagemaker, M., *Nano Lett.*, **2014**, *14*, 2279). Copyright (2014) American Chemical Society.

Recent investigations have focussed on the dependence of the redox mechanism on the cycling rate. Depending on how far from the equilibrium each particle is, the particle size distribution and electronic conductivity of the electrode, different kinetic pathways may exist.^{91,92,93,94} The intermediate phase $\text{Li}_{\sim 0.6}\text{FePO}_4$ is formed, as predicted by Monte-Carlo simulations⁹⁵, at medium (C/5) or high rates (10C) depending on the particle size, but it evolves

1
2
3 at open-circuit towards the thermodynamically stable mixture of Li-rich $\text{Li}_{1-x}\text{FePO}_4$ and Li-poor
4 Li_xFePO_4 end-members. A larger distribution of solid solution compositions Li_xFePO_4 was
5 observed upon cycling of LiFePO_4 nanoparticles at even higher rates (for instance at 60C)
6 (Figure 6). These recent results allow to rationalize the uncommon high rate capabilities of
7 LiFePO_4 despite its redox mechanism consisting (at the equilibrium) of a two phase reaction
8 between two end members showing very bad transport properties. The strains induced at the
9 reaction front by cycling conditions out of the equilibrium promote the formation of solid
10 solutions with small polarons $\text{Fe}^{2+}/\text{Fe}^{3+}$, higher electronic conductivities and thus the possibility
11 for lithium to diffuse at high rates, as it was also recently demonstrated for the olivine
12 Na_xFePO_4 .^{12,96,97}

13
14
15
16 The fundamental research performed over the last ten years on LiFePO_4 is a nice example of
17 how synergies between experimental and theoretical research can step by step pave the way
18 for a better understanding of the material and its operation mechanisms. However, this
19 wouldn't have been possible without the development of in-situ characterization
20 tools,^{98,99,100,101} enabling to probe the mechanisms involved at all length scales (material,
21 electrode and battery), whatever the state of charge or discharge, the cycling rate, the storage
22 and aging conditions ...

23
24
25 Olivine phases containing alternative transition metal ions such as LiMnPO_4 , LiCoPO_4 and
26 LiNiPO_4 have also been investigated. While the two latter do exhibit too high operation
27 potentials to be used with common electrolytes, LiMnPO_4 operates at ca. 4.1 V vs. Li^+/Li , and
28 exhibits an attractive theoretical capacity (170 mAh/g). Yet, its practical development has
29 been plagued with a myriad of difficulties (poor electronic/ionic transport properties, chemical
30 instability in the charged state ...).⁸² Despite the fact that a large diversity of synthetic
31 strategies has been explored to yield smaller particles and composites,^{82,102} the above
32 mentioned shortcomings are not overcome and the electrochemical performance remains
33 poor, especially at rates higher than C/5. Nevertheless, $\text{LiMn}_y\text{Fe}_{1-y}\text{PO}_4$ ¹⁰³ for $y < 0.6$ has been
34 found to exhibit a reversible capacity close to that of LiFePO_4 (for similar particle size) with
35 higher average potential and very good rate capability.¹⁰⁴ As for LiFePO_4 , solid solutions
36 mechanisms would be at the origin of remarkable fast lithium diffusion in these Mn and Fe
37 mixed compositions¹⁰⁴ as well as in vanadium-substituted LiFePO_4 .¹⁰⁵

38
39
40
41
42 Research on these alternative polyanionic materials has been boosted by the success of
43 LiFePO_4 and the large panel of compositions and structures with different metal and different
44 polyanions is available to the solid state chemist (See Figure 7).^{82,106} The targets are achieving
45 large energy densities by enhancing the operation potential, increasing the capacity through
46 the number of electrons (lithium ions)¹⁰⁷ exchanged per transition metal ion considering two-
47 electron couples as $\text{Ni}^{2+}/\text{Ni}^{4+}$, $\text{V}^{3+}/\text{V}^{5+}$ and $\text{Fe}^{2+}/\text{Fe}^{4+}$, and increasing the capacity through a
48 decrease in the formula weight, considering for instance borates as an alternative to
49 phosphates. Nevertheless, finding new polyanionic positive electrode materials with attractive
50 properties remains challenging. Those that deserve in our opinion special attention are
51 described below.

52
53
54
55
56 Sulfate chemistry has been intensively explored in the last few years and, as a result, many
57 new materials with different structures and compositions have been synthesized^{108,109,110,111,112}:
58 the Tavorite, Silimanite and Triplite LiMSO_4F , the layered LiMSO_4OH and the Marinite

$\text{Li}_2\text{M}(\text{SO}_4)_2$ (Figure 8). Iron based compounds are of peculiar interest as iron is an abundant element. They can exchange almost one electron per mol, especially when coated with a conducting polymer.¹¹³ The clever use of the inductive effect, as nicely exemplified by J.B. Goodenough et al.^{114,115} in Nasicon-type structure $\text{Li}_x\text{M}_2(\text{XO}_4)_3$ ($\text{M} = \text{V}, \text{Fe}, \text{Ti} \dots$; $\text{X} = \text{P}, \text{W}, \text{S}$), has enabled to tailor the potential of the $\text{Fe}^{2+}/\text{Fe}^{3+}$ redox couple in the Tavorite framework LiFeXO_4Y ($\text{X} = \text{P}, \text{S}$; $\text{Y} = \text{OH}, \text{F}$) from 2.6 to 3.6 V vs. Li^+/Li , and then moving to the Triplite and Marinite polymorphs to values well above that observed for the olivine $\text{LiFe}^{\text{II}}\text{PO}_4$ (3.45 V). Triplite LiFeSO_4F delivers the highest voltage at 3.9 V vs. Li^+/Li , and understanding the driving force behind difference in potential between the two LiFeSO_4F polymorphs¹¹⁶ is crucial, as it can foster the development of other polyanionic families such as pyrophosphates¹¹⁷. The Triplite LiFeSO_4F illustrates that materials with disordered structure (Li/Fe occupy the same octahedral site) can exhibit high energy density if organized enough to create a 3D diffusion pathway for fast lithium diffusion. From a “practical” application perspective, low cost synthesis, optimized morphologies and composites have still to be developed to get the highest reversible capacity and cyclability for such compounds.

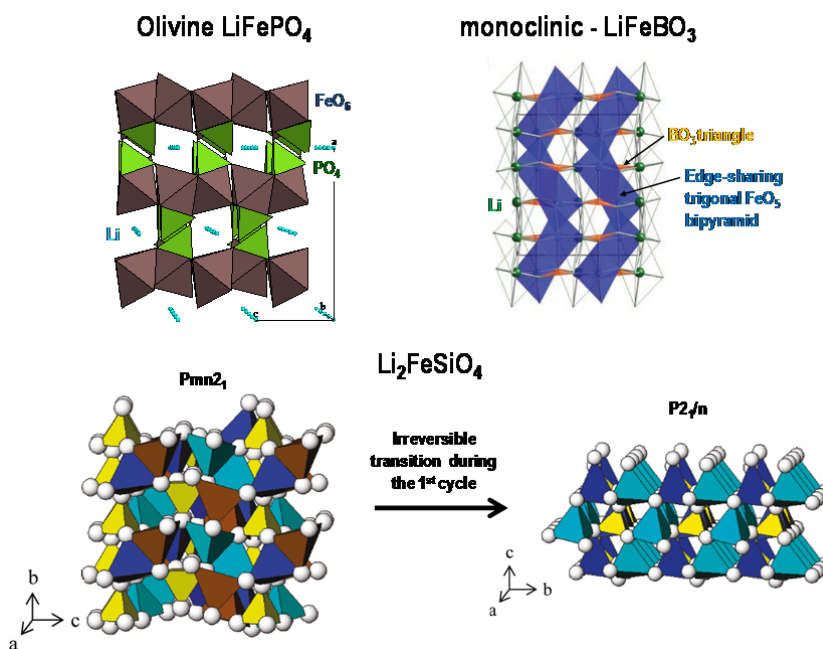


Figure 7: Description of different polyanionic structures: the olivine LiFePO_4 , the monoclinic LiFeBO_3 ¹¹⁸ (Adapted from Yamada, A.; Iwane, N.; Harada, Y.; Nishimura, S.; Koyama, Y.; Tanaka, I. *Adv. Mater.*, **2010**, *22*, 3583 Copyright © 2010 WILEY-VCH Verlag GmbH & Co. KGaA, Weinheim) and $\text{Li}_2\text{FeSiO}_4$ as pristine and after the 1st cycle¹¹⁹ (adapted with permission from Armstrong, A.R.; Kuganathan, N.; Islam, M.S.; Bruce, P.G. *J. Am. Chem. Soc.*, **2011**, *133*, 13031 Copyright (2011) American Chemical Society).

Phosphates showing Tavorite framework LiMPO_4Y ($\text{M} = \text{Fe}, \text{Ti}, \text{Mn}, \text{V} \dots$; $\text{Y} = \text{F}, \text{O}, \text{OH}$) are appealing as they exhibit a wide compositional spectrum.⁸² The V-based compounds, $\text{LiV}^{\text{III}}\text{PO}_4\text{F}$ and $\text{LiV}^{\text{IV}}\text{PO}_4\text{O}$, are attractive due to fast lithium diffusion at high voltage (> 4.0 V vs. Li^+/Li), and the possibility to exchange two electrons per metal (with the involvement of the redox couples $\text{V}^{4+}/\text{V}^{3+}$ and $\text{V}^{3+}/\text{V}^{2+}$ for the former and $\text{V}^{5+}/\text{V}^{4+}$ and $\text{V}^{4+}/\text{V}^{3+}$ for the latter). Nonetheless, the reversible capacity really achieved (140 mAh/g) corresponds to one electron per metal, as the difference between the two redox couples is > 1.5 V –too large value for practical

consideration.^{120,121,122,123,124} Even in such circumstances, LiVPO_4F and LiVPO_4O remain of interest as they deliver the highest energy density amongst all the polyanionic materials reported, with phosphates ensuring chemical and thermal stability. Silicates $\text{Li}_2\text{M}^{\text{II}}\text{SiO}_4$ ($\text{M} = \text{Fe}, \text{Mn}, \text{Ni}$) can also exhibit a wide range of polymorphs and compositions with Li, M and Si occupying tetrahedral sites and Li and M being ordered or statistically distributed.^{125,126,127} Again, the interest in these materials resides in the abundance of both Fe and Mn and the possibility of exchanging two electrons per transition metal, which has unfortunately not been achieved to date. The current research focus is engineering of particle size, morphology, carbon coating ..., in order to optimize the electronic wiring between the nanoparticles, the lithium diffusion within the particles, and thereby electrochemical performance.^{128,129,130} Nonetheless, both the rate capability and reversible capacity (most often given for a wide potential window 1.5 – 4.8 V vs. Li^+/Li) remain poor.¹³¹

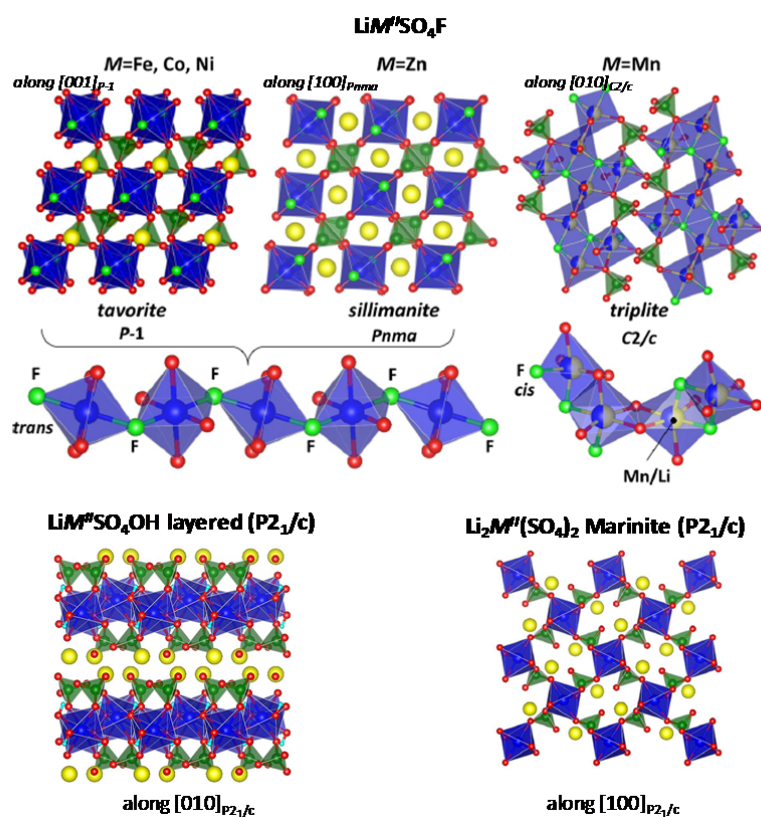


Figure 8: Comparison of the different structures obtained for LiMSO_4F , LiMSO_4OH and $\text{Li}_2\text{M}(\text{SO}_4)_2$. MO_4F_2 and MO_6 octahedra are displayed in blue, SO_4 tetrahedra in green and the Li^+ ions as yellow balls. Tavorite and Sillimanite are viewed perpendicular to the MO_4F_2 corner-sharing chains. For the Triplite, the MO_4F_2 octahedra are built of four oxygen and two fluorine atoms and they are statistically filled with Li and M. For the layered hydroxysulfates, the layers are made of corner-sharing chains. For the Marinite, each MO_6 octahedron is isolated and surrounded by six sulfate groups. Adapted with permission from¹⁰⁸ (Rousse, G.; Tarascon, J.M. *Chem. Mater.* **2014**, *26*, 394). Copyright (2014) American Chemical Society.

Last but not least, borates are especially interesting due to their lower formula weight.¹³² $\text{LiM}^{\text{II}}\text{BO}_3$ ($\text{M} = \text{Fe}, \text{Mn}, \text{Co}$) are investigated and diverse strategies such as engineering of the active nanoparticles are attempted to reach high reversible capacity,^{133,134,135,136} but success is very limited for LiFeBO_3 (130 mAh/g vs. the theoretical 210 mAh/g at C/20 and 55°C, within a

1
2
3 large voltage window 2.0 – 4.5V vs. Li⁺/Li) ¹³⁷ and even worse for LiMnBO₃ and LiCoBO₃.^{138,139}
4 Interestingly, capacity values close to theoretical (201 mAhg⁻¹) at C/50 and room temperature
5 have been reported for LiMn_{0.5}Fe_{0.4}Mg_{0.1}BO₃,¹⁴⁰ although the origin of this remarkable behavior
6 (i.e. easier lithium diffusion for that peculiar composition) remains to be understood.
7

8
9 Overall, phosphates and sulfates remain the most attractive playground for the research of
10 new positive electrode materials. Several compounds exhibiting rather fast lithium diffusion
11 and thus good reversible capacity and cyclability have already been identified, even if
12 optimization of the particle size and of the electrode formulation is often required to achieve
13 decent performance. The main penalty of sulfates versus phosphates is their solubility, which
14 prevents any electrode slurry preparation in water and causes accelerated ageing upon
15 storage. After years of research devoted to borates and silicates, little progress has been
16 achieved due to (i) the difficulty to control the synthesis (purity and nature of the polymorph)
17 and (ii) the very bad transport properties associated to the presence of defects at the surface
18 of the material or within the bulk and irreversible structural modifications observed upon
19 cycling. Alternative syntheses are widely developed to design new materials and new
20 structures, especially at low temperature using sometimes biology inspired processes.¹⁴¹ As an
21 example, a myriad of new sulfate polymorphs were for instance recently obtained using
22 ionothermal methods.^{142,143,144} On another ground theoretical studies have revealed to be a
23 very powerful tool to predict defect chemistry (Li/M disorder, extra M in the cavities ...),
24 surfaces' energy, lithium diffusion pathways ... to guide the solid state chemist in tailoring the
25 shape (size and growth according to preferential orientations) and the stoichiometry of the
26 particles for optimized performances^{145,146} while also bringing insights on the stable electronic
27 and crystal structures. In contrast the identification of new materials from scratch by
28 theoretical approaches¹⁴⁷ can still be challenged by intuition of the experienced chemist.¹⁴⁸
29
30
31
32
33
34

35 3. ALTERNATIVE REACTION MECHANISMS

36
37 Materials that exhibit a non-insertion based redox reaction mechanism with lithium are not
38 new, as the electrochemical formation of alloys was already demonstrated in the 1970's¹⁴⁹ and
39 the first reports on partial reversibility for the mechanism currently termed "conversion
40 reaction"¹⁵⁰ also trace back to the 1980's.¹⁵¹ The main advantage of such alternative reaction
41 pathways (see Figure 9) is the large increase in electrochemical capacity (i.e. moles of
42 lithium/electrons reacted per mol of material), while the main drawback is that this is only
43 achieved at the expense of major structural changes, which are obviously caused by the large
44 modification in the composition of the material. As an example, the formation of Li₁₅Si₄ for Si
45 electrodes results in an increase of 375% in the number of atoms present in each active
46 particle with electrochemical capacities of 8363 mAh/cm³ and 3589 mAh/g, much larger than
47 the 975 mAh/cm³ and 372 mAh/g achieved for graphite (formation of LiC₆ with 16% increase in
48 the number of atoms per active particle). Unfortunately, these changes are difficult to
49 "buffer", even with the use of sophisticated strategies and typically result in cycling
50 performance penalties. While significant advances were made for alloys and some seem to be
51 almost on the commercialization pipeline, the progress in overcoming the bottlenecks
52 associated to conversion reactions is stagnating and prospects of practical application
53 vanishing.
54
55
56
57
58
59
60

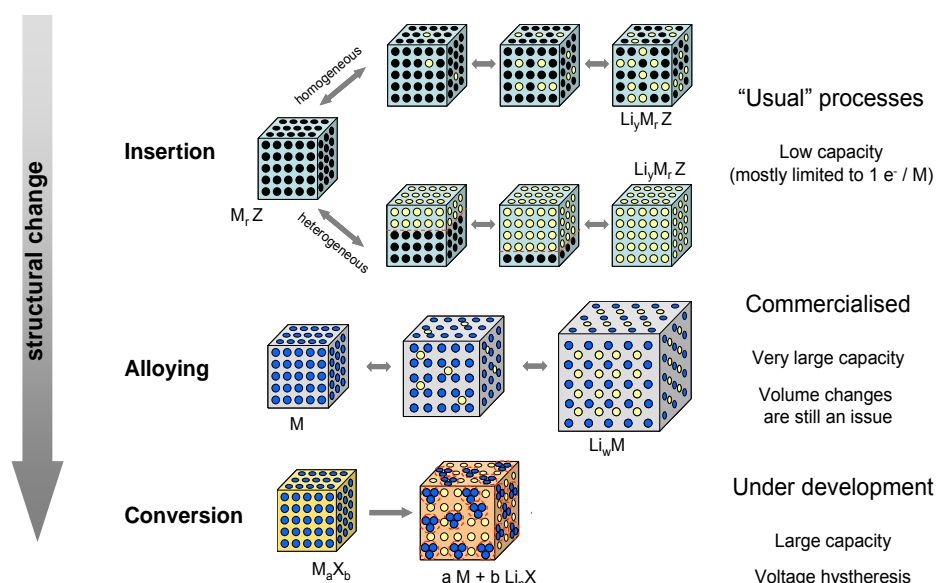


Figure 9. Schematic representation of different reaction mechanisms observed in electrode materials for lithium batteries. Black circles: voids in the crystal structure, blue circles: metal, yellow circles: lithium. Reproduced from¹⁵² (Palacin, M.R. *Chem. Soc. Rev.* **2009**, *38*, 2565) with permission from The Royal Society of Chemistry.

3.1. ALLOYS

Alloying reactions between lithium and a large number of metallic or semi-metallic elements have proved feasible in electrochemical cells at room temperature in conventional organic electrolytes and have been widely studied.^{153,154} Considerations of achievable capacities coupled to abundance, cost and toxicity restrict the systems deserving interest for application¹⁵⁵ to a handful of choices; Si, Sn, Al and Pb, with the first two clearly being the most attractive (3589 mAh/g – 8363 mAh/cm³ and 991 mAh/g - 7233 mAh/cm³ for Si and Sn, respectively) with Si having deserved most attention in recent years. The practical utilization of alloy electrodes is handicapped by the huge volume changes associated to the (de)alloying process, which result in the introduction of large strains in the particles that promote micro-crack formation and propagation. Such changes lead upon cycling to a progressive de-cohesion, particle shuffling, and, subsequently, to severe capacity fading. A wide spectrum of materials engineering strategies has been developed¹⁵⁵ to limit the effects of these volume changes, based on different considerations such as the better accommodation of volume changes for particles that are amorphous, nano-sized and less prone to break upon stress, or porous,¹⁵⁶ since the available voids could be filled during the volume expansion. Along the same line, the use of active particles embedded in a conducting matrix (i.e. carbon) which could buffer the volume expansion has also been widely explored. Unfortunately these approaches do also involve drawbacks related to the use of nano-sized materials such as lower tap densities and higher surface/volume ratios, and promote enhanced reactivity with the electrolyte. Another successful alternative, although probably tricky to implement at the full cell level, is the limitation in the extent of reduction proposed for silicon in 2007.¹⁵⁷ Non-reacted silicon at the core of particles remains crystallized and helps in limiting the loss of integrity for the outer shell, which reacts and turns and remains amorphous during the lithium uptake and removal. The fundamentals of this approach are essentially the same as the use of

thin active material films on an inert substrate so that reduction induces an expansion which is constrained to the direction perpendicular to the film. In this case, and in line with the above mentioned strategies, amorphous films are preferred to avoid any anisotropic expansion of oriented grains during alloying. Intermetallics (MM') have also been studied where M' (Mn, Fe, Co, Ni, Cu, Nb, ..) does not alloy with lithium (and hence brings about a decrease in the overall capacity) but contributes to buffer volume changes. In this case, the reduction process entails a displacement reaction with "extrusion" of M' concomitant to the formation of the Li_xM alloy.^{158,159,160} Similarly, but involving two metal forming alloys, the pseudo-binary Sn-Si-C system has been addressed through combinatorial sputtering methods,¹⁶¹ as Sn-Si alloys are specially interesting by their improved electrical conductivity and phase stability and carbon inhibits Sn segregation.

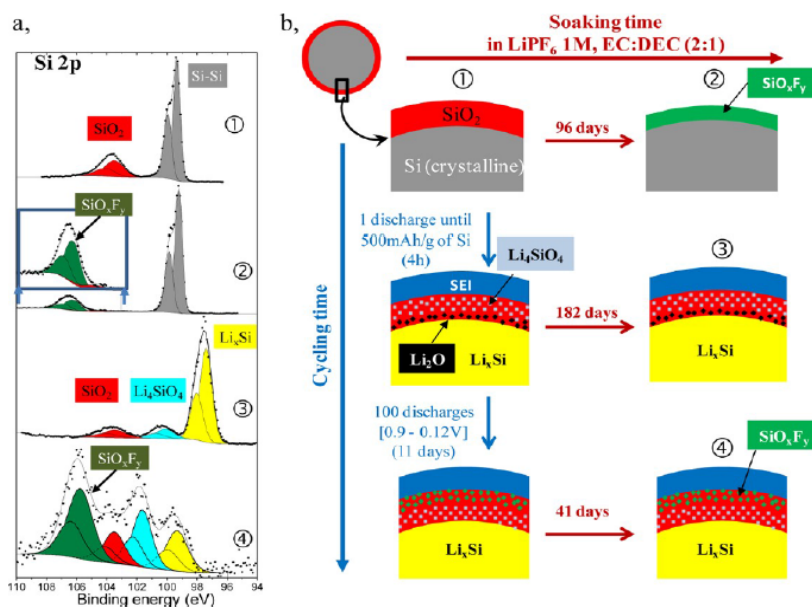


Figure 10. (a) Si 2p spectra (in-house PES, 1486.6 eV) of ① a silicon based pristine electrode, ② an electrode after 96 days in contact with the electrolyte, ③ after a first reduction to provide 500 mAh/g_{Si} and ④ after the 100th reduction to 0.12V. (b) Schematic view of the layer formed on the silicon particle surfaces during cycling and/on storage with the electrolyte. Reprinted with permission from¹⁶⁵ (Philippe, B.; Dedryvere, R.; Gorgoi, M.; Rensmo, H.; Gonbeau, D.; Edstrom, K. *Chem. Mater.* **2013**, *25*, 394). Copyright (2013) American Chemical Society.

All those strategies are linked to the use of substrates (dense films, limited reaction), voids (porous powders), matrix (composite materials), all inactive or kept un-reacted and therefore leading to a penalty in energy density. Moreover, capacities reported for these composites in the literature have to be taken with care, as they are often specified with respect to the mass of active material and not of composite. Despite all such drawbacks, these strategies have enabled huge improvements in performance with respect to graphite at the laboratory scale, mostly in the so termed "half-cells" using lithium counter-electrodes. However, a proper assessment of the capacity retention in full cells against conventional positive electrodes is still a crucial issue¹⁶² not trivial to solve. For the latter, electrode balancing (the ratio between positive and negative) can be an issue, as the lithium supply is limited by the positive electrode and thus the effect on capacity fading can be dramatic. While coating the material with lithium metal to compensate for first cycle low coulombic efficiency (mostly related to the formation of the SEI and concomitant loss of lithium)¹⁶³ should help in alleviating such effects, up-scaling

of the production would be by no means trivial. Overall, the progress needed to reach the market advances at slow pace, and only a few percents of Si is present in Si-C composites commercially used today.

The development of long cycle life electrodes is also correlated to the ability to engineer a stable SEI. While its composition mostly depends on the electrolyte used and thus, should not dramatically differ from the SEI observed for graphite negative electrodes,^{2,3,4} minor changes can play important roles for long term stability and capacity retention. Thorough non-destructive depth resolved XPS studies on SEI grown on silicon containing electrodes have enabled to point out the existence of interfacial phase transitions involving reactivity of the native SiO₂ layer with lithium to form a lithium silicate and a fluorinated SiO_xF_y phase arising from reactivity with HF impurities,^{164,165} the microstructure/nature of the SEI depending on the history of the cycling (Figure 10).

All such findings need to be seriously taken into account as the role of the SEI layer is much more critical for alloying materials than for conventional insertion electrodes. Indeed, the SEI will break if its endurance limit is exceeded by the amplitude of the stresses generated at the electrode and fresh naked electrode surface will form on which an additional SEI would start to grow. If this is continuous, it would ultimately result in cell failure due to electrolyte consumption and loss of electrode porosity, with a decrease in its effective surface area and concomitant increase in its polarization.¹⁶⁶ Thus, SEI engineering strategies to promote SEI with enhanced stability and elasticity, involving for instance the use of additives, are crucial.^{167,168,169}

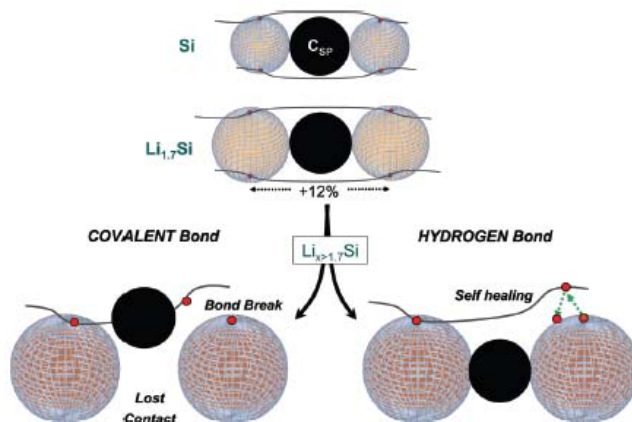


Figure 11. Schematic model showing the evolution in the CMC-Si bonding as lithium uptake proceeds, from top to bottom. Up to 1.7 Li/Si, both covalent and hydrogen bonding can sustain the particle volume changes, the overall swelling being buffered by the electrode porosity. Beyond 1.7 Si/Li, the maximum CMC stretching ability is reached and only the hydrogen-type Si-SMC interaction allows preservation of the efficient network through a self-healing process. Reproduced with permission from¹⁷³ *J. Electrochem. Soc.*, 2011, **158**, A750. Copyright 2011, The Electrochemical Society.

Electrode engineering through formulation is also vital. While the chain polymeric network of PVDF (commonly used in graphite based electrodes) inducing electrode elasticity was believed to help in preventing particle disconnection for alloy based electrodes, the good performance of micron-size silicon particles¹⁷⁰ using a very brittle polymer such as carboxymethylcellulose (CMC) came as a surprise. These findings were rationalized through elucidation of the silicon-binder interactions,^{171,172,173} as the bonds between the carboxyl groups of CMC and SiO₂ on the

1
2
3 particle surface were proposed to re-form if locally broken and hence exhibit a self-healing
4 effect.¹⁷⁴ (Figure 11) The promising results achieved with CMC prompted the study of other
5 binders exhibiting carboxyl groups such as PAA (polyacrylic acid) or polysaccharides^{175,176} and
6 grants for further improvement through polymer design strategies.^{177,178} On a related aspect,
7 the reactivity of nano-sized particles which may show catalytic activity towards the liquid
8 medium used in electrode fabrication can also be an issue, which is also currently being
9 addressed by tuning the SiO₂ surface layer.¹⁷⁹
10
11

12 In summary, intense research efforts have resulted in important gains in performance and
13 rational understanding of the reactivity of these complex systems, which holds promise for
14 additional progress and gradual penetration of silicon based electrodes in commercial cells.
15

16 3.2. CONVERSION REACTIONS 17

18 Conversion reaction is the term usually applied to define the reaction of a binary transition
19 metal compound, M_aX_b (M=transition metal, X=O, S, N, P, F, H...) with lithium to yield metallic
20 nanoparticles embedded in a matrix of Li_yX according to: M_aX_b + (b·n) Li ↔ a M + b Li_nX
21 where *n* is the formal oxidation state of X. The typical potential vs. composition profile of such
22 materials is depicted in Figure 12. Depending on the starting compound some insertion of
23 lithium in the pristine structure to form a ternary Li-M-X intermediate may take place at the
24 beginning of reduction and this phase can further react through the conversion reaction itself,
25 in other cases, if M does electrochemically form alloys with lithium, the conversion process
26 may be followed by an alloying reaction. Independently of the complexity of the overall redox
27 mechanism, the conversion step involving full reduction of the transition metal to its elemental
28 state results in large capacity values, with for instance theoretical values of 700-1000 mAh/g
29 for most oxides.¹⁸⁰ The key to the observed reversibility of the process upon subsequent
30 oxidation seems to lie in the large amount of interfacial surface which makes nanoparticles
31 very active toward the decomposition of the lithiated matrix. Even if simple at a first glance,
32 such reactions induce a strong structural re-organization which, as in the case of alloys, may
33 result in particle decohesion and unsatisfactory cycling performance.
34
35
36
37
38

39 The potential vs. composition profile for conversion electrode materials does exhibit some
40 characteristic features (see Figure 12), namely (i) low coulombic efficiency (i.e. important
41 irreversible capacity (IC)) on the first cycle, which exhibits a unique profile significantly
42 different from the following ones, (ii) an additional extra capacity with respect to theoretical
43 values (EC), its signature being a sloping curve that follows the conversion plateau and (iii)
44 large potential hysteresis (H) between oxidation and reduction (i.e. charge and discharge)
45 which causes a large penalty in roundtrip energy efficiency and constitutes the major
46 shortcoming to practical application for this kind of materials. The irreversible capacity has
47 been ascribed to a limited reversibility of the reaction either due to the existence of electrically
48 disconnected regions/particles within the electrode, as observed by in situ TEM¹⁸¹ and/or to
49 the re-conversion to other phases than the initial compound (e.g the product of Co₃O₄
50 reduction forming CoO upon first reoxidation). As for the extra capacity (EC) phenomenon,
51 two alternative explanations were initially proposed: interfacial charge storage^{182,183} in a
52 capacitive-like manner and electrolyte degradation,^{184,185} with recent studies¹⁸⁶ indicating that
53 interfacial storage would only account for a small percentage of the experimentally observed
54
55
56
57
58
59
60

capacity, the rest being faradaic and fully related to electrolyte decomposition enhanced by the metal nanoparticles generated upon reduction. In the case of RuO_2 the process has been shown to be associated to the generation of LiOH and its subsequent reversible reaction with Li to form Li_2O and LiH .¹⁸⁷ Such parasitic side reaction would most probably end up in cell failure upon the long term due to electrolyte consumption, but may be addressed by strategies involving active material particle coating, such as those discussed above for positive electrode materials operating at high potential, or by the use of alternative electrolytes.¹⁸⁸

The origin of hysteresis (H) is still controversial. Electronic conductivity measurements carried out *in situ* in the course of reduction¹⁸⁹ rule out ohmic polarization as the main cause. This is also consistent with the fact that conversion electrodes can simultaneously show large voltage hysteresis and fast kinetics, i.e. when nanostructured current collectors are used¹⁹⁰ or with the fast conversion processes observed through real-time imaging.¹⁹¹ Moreover, first principles modeling on the Li-FeF_3 system revealed an inherent difference in reaction path between reduction and oxidation, determined by the limitations imposed by the need to transport a second species (e.g. Fe or F) in addition to Li .¹⁹² Experimental studies using a large spectrum of techniques, including NMR, pair distribution function (PDF) analysis, and high throughput electron microscopy techniques have allowed to confirm this trend not only for FeF_3 but also for $\text{FeO}_x\text{F}_{2-x}$.^{193,194} DFT calculations on CoO and CoP considering the relative stability of the different interfaces that can be formed during the conversion process also point to an asymmetry of the chemical and electrical responses upon reduction and oxidation.^{195,196} The computed data are in very good agreement with experimental results, the different potentials observed upon oxidation and reduction would be related to the growth of diverse interfaces which induce different electrochemical equilibria (see Figure 12). These findings have important implications, as strategies based on the reduction of diffusion lengths or the improvement of charge transfer kinetics, widely reported in the literature for materials operating through a conversion reaction mechanism, are clearly unlikely to produce any improvement in the hysteresis observed.

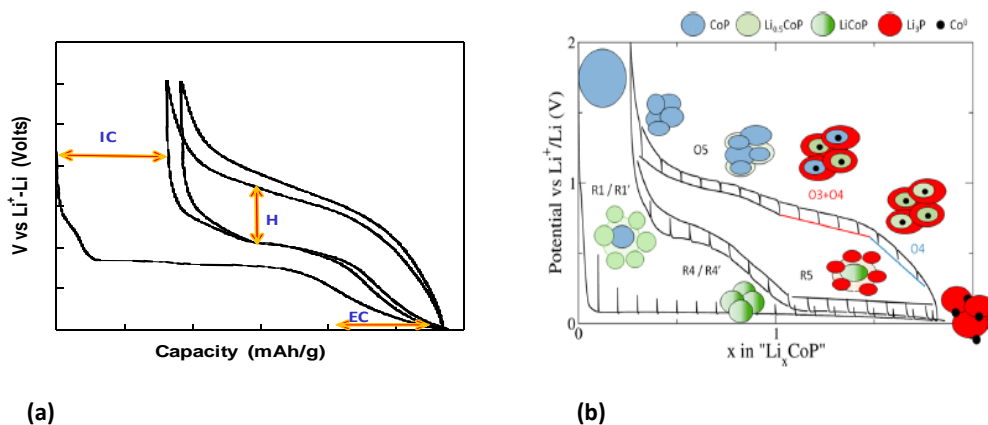


Figure 12: (a) Typical potential vs. composition profile of the first two and half cycles for an electrode containing a material that reacts through a conversion reaction. The irreversible capacity (IC) upon the first cycle, extra capacity (EC) and potential hysteresis (H) are denoted by orange arrows. (b) GITT measurements carried out on a CoP/Li cell with steps of 1h at C/10 (both upon oxidation and reduction) and rest to open circuit voltage until the potential slope is less than 30 mV/h. The experimental values are compared with theoretical predictions (colored lines for each step). (b) is reprinted with permission from¹⁹⁶ (Khatib, R.; Dalverny, A.L.; Saubanere, M.; Gaberscek, M.; Doublet, M.L. *J. Phys. Chem. C* **2013**, *117*, 837.). Copyright (2013) American Chemical Society.

1
2
3 The operation potential of conversion reaction materials does obviously depend on both the
4 transition metal and the anionic species, so that, in principle, a wide spectrum of choices
5 would be available for different materials. Transition metal fluorides have the peculiarity to
6 exhibit relatively high ($> 2V$ vs. Li^+/Li) potentials, as a result of the very high ionicity of the M-F
7 bond, and hence are the only class of conversion reaction compounds suitable to be used as
8 positive electrodes. They are, however, typically insulating and exhibit the largest potential
9 hysteresis amongst all reported conversion reaction materials. Overall, oxides are by far the
10 family of compounds that has attracted the most attention, with conversion reactions
11 reported for a large diversity of phases¹⁹⁷ in the potential range 0.2-1.4 V vs. Li^+/Li . The
12 exception are those containing transition metals in groups 4 and 5, which would require much
13 lower potentials to attain full reduction to metallic state.
14
15

16
17 Iron sulphides (both FeS_2 and FeS) which were studied in the 1980's in high temperature cells
18 with molten salt electrolytes but abandoned due to their limited reversibilities, have recently
19 been reinvestigated, together with nitrides, phosphides and even hydrides with only moderate
20 success.¹⁸⁰ In the case of nitrides, phosphides and certain sulphides, the redox centers are not
21 exclusively located on the transition metal, but electron transfer occurs into bands that have a
22 strong anion contribution, similarly to what has been mentioned above for some Li-rich
23 layered positive electrode materials.¹⁹⁸ Hydrides have not deserved much attention and the
24 few studies available reveal important capacity fading, but they remain the most interesting
25 family to study from the fundamental point of view as they show the lowest hysteresis values
26 reported.^{199,200}
27
28
29

30
31 Overall, numerous studies on conversion reaction materials are available, largely focusing on
32 improving cycle life and, to a lesser extent, on the coulombic efficiencies. Partial success is
33 achieved through electrode engineering strategies such as forming nano-composites with
34 nano-sized active materials and a considerable amount of carbon. However, the practical
35 relevance of thus results remains to be proven as particle reorganization and volume changes
36 upon cycling are still likely to modify these nano-structures. Comparative studies of the
37 performance of electrodes made of nano- and micron-sized particles offer diverging results,
38 with the latter sometimes outperforming the former due to issues related to active material
39 dissolution and catalytic activity towards electrolyte decomposition. It is unfortunate that a
40 significant part of the publications dealing with conversion reaction materials do exclusively
41 provide a plot of capacity vs. cycle number to illustrate electrochemical performance, which
42 does not allow to fully grasp the magnitude of the hysteresis. All in all, this is the main issue to
43 tackle if such materials are ever to be seriously considered for any applications. Time will tell
44 whether current research will result in a "natural selection" yielding some specific compounds
45 (maybe hydrides even if they are currently not receiving any major attention) for which
46 technological research can result in application prospects, as has been the case for silicon in
47 alloys.
48
49
50
51

52 53 54 55 **4. CONCLUSIONS AND PERSPECTIVES**

56
57 Contrary to what *a priori* could be expected from the tremendous amount of research devoted
58 to lithium ion electrode materials and described in the previous sections, materials science
59
60

development in the battery field is still crucial. Indeed, the energy density of cells will only significantly increase if the cell voltage and capacities of electrode materials are improved and the possibility of fast recharge can only be achieved through enabling redox reactions with fast kinetics. At the same time the extended cycle life must be maintained. Defining research strategies has to be made with due care in order to avoid following approaches proven unsuccessful in the past (the vast amount of literature available unfortunately largely contributes to overseeing previous meaningful work) and employ realistic targets. For instance, the compulsory presence of inert cell components makes the total increase in energy density of the cell with improving negative electrode capacities negligible after a certain threshold value²⁰¹ if the positive electrode capacities are not enhanced (Figure 13). Thus, if promises of commercialization for negative electrodes with a significant amount of silicon hold true, research efforts should target the positive counterpart. In view of the current state of the art, Li-rich layered oxides are most probably the most promising track to follow, with the reversible participation to the redox processes of oxygen anions and of 4d and 5d transition metal cations, the latter for some materials being able to exchange more than one electron per metal. A few alternatives would be Ru, Mo or W though some of them are not viable from the practical point of view due to solubility, cost and/or abundance constraints. The polyanionic materials exhibit higher thermal stability, but are strongly penalized by a higher molecular weight. Success in the quest of the second electron per transition metal, if ever achieved, would undoubtedly bring these compounds to the front of the scene.

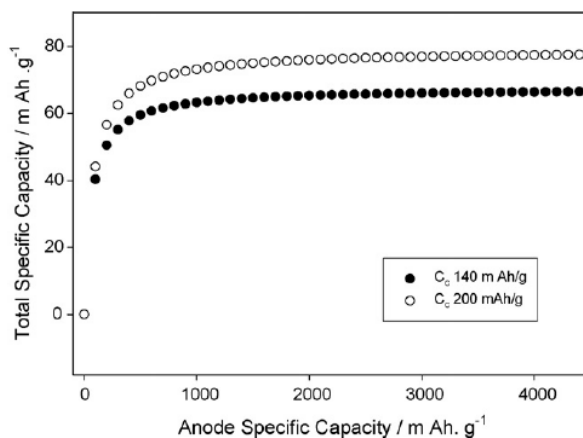


Figure 13. Total capacity of a 18650 Li-ion cell as a function of the negative electrode (anode) capacity (C_a), (calculated taken into account the mass of inert cell components) for two different positive electrodes with capacities of 140 mAh/g (black filled circles) and 200 mAh/g (empty circles). Reprinted from²⁰¹ *J. Power Sources* **2007**, 163, 1003. Kasavajjula, U.; Wang, C.; Appleby, A.J « Nano- and bulk- silicon-based insertion anodes for lithium-ion secondary cells » Copyright (2007), with permission from Elsevier.

On the other hand, further attention to increased energy densities through the development of very high potential positive electrode materials must by all means be coupled to advances in electrolytes able to withstand such potentials without decomposing.

The advent of the lithium ion battery technology and its continuously enhanced performance has been promoted by the development of inorganic electrode materials and the progresses in the basic understanding of their operating mechanisms at the atomic scale thanks to the ever improving characterization tools. Indeed, *in situ* or *operando* experiments are becoming routine or relatively common (X-ray or neutron diffraction^{94,98,99,100,101} and also magnetic properties,²⁰² Differential Electrochemical Mass Spectroscopy (DEMS)⁴⁰ or Raman

1
2
3 spectroscopy²⁰³) and efforts are carried out to adapt alternative characterization tools
4 requiring specific environments (in situ TEM). The aim is to characterize electrodes probing all
5 possible length scales from the atomic (NMR) to the electrode (tortuosity, tomography,
6 magnetic resonance imaging),^{204,205} including the SEI,²⁰⁶ in order to ultimately enhance
7 performance but also to understand ageing processes²⁰⁷ (much more complex to tackle) to
8 enhance cycle life and thereby total energy throughput.
9

10
11 The basic research is evolving from the classical synthesis, characterization, and
12 electrochemical testing approaches to embrace as well the technological aspects. Indeed,
13 figures of merit for performance depend not only on the electrochemical testing parameters,
14 but also on the electrolyte, electrode formulation (type and amount of carbon and binder),
15 and electrode architecture (thickness, porosity, active material loading etc). Moreover, such
16 studies more and more often involve moving from the model half-cells probing vs. lithium
17 counter-electrodes to the assembly of full cells, the latter forcing control of the SEI formation
18 as well as careful electrode balancing, even at the laboratory scale.
19

20
21 The electrode slurry formulation has in the past largely been based on empirical observations
22 and often kept as undisclosed industrial know-how. The topic has gradually captured also the
23 interest of the academic community, why appealing correlations have been established
24 between the type of polymer used as binder, the suspension rheological properties, the
25 morphology (thickness, tortuosity, etc)^{208,209} and mechanical properties of the dried composite
26 electrode, and the resulting electrochemical properties.^{210,211,212,213,214} As current commercial
27 cells do contain ca. 50% of inert components, a clear path to follow is the development of thick
28 electrodes (>300 μm) with effective performance, which would also result in a cost decrease.
29 This involves control of electrode architecture and porosity to ensure good kinetics for mass
30 transport.
31

32
33 As a battery is an alive chemical reactor, gaining control of the performance through tuning
34 materials properties require deep fundamental understanding of the processes taking place at
35 all levels. There is no doubt that following such an integral approach will accelerate progress
36 and help in selecting the most viable system for each application.
37

38
39 In conclusion, materials chemistry continues to be the essential part of battery research and
40 we are confident that with the currently available tools and focussing our efforts in the key
41 current shortcomings, breakthroughs will certainly be unravelled in the years to come.
42

43 44 45 46 47 **ACKNOWLEDGEMENTS**

48
49 We acknowledge ALISTORE-ERI and RS2E members for sharing fruitful discussions and Prof.
50 Patrik Johansson, Prof. Dominique Larcher and Dr Michel Ménétrier for critical reading of the
51 text. We are grateful to Ministerio de Ciencia e Innovación (Spain, grant MAT2011-24757),
52 CNRS and Région Aquitaine for financial support. L. Croguennec is grateful to C. Delmas,
53 M. Ménétrier, D. Carlier, F. Weill and C. Masquelier for their cooperative researches and
54 valuable comments on different oxides and polyanionic systems as electrode materials for
55 Lithium-ion batteries.
56
57
58
59
60

REFERENCES

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- ¹ Whittingham, M.S. *Prog. Solid St. Chem.* **1978**, *12*, 41
- ² Xu, K.; *Chem. Rev.* **2004**, *104*, 4303.
- ³ Aurbach, D. *J. Power Sources* **2000**, *89*, 206.
- ⁴ Verma, P.; Maire, P.; Novak, P. *Electrochim. Acta* **2010**, *55*, 6332.
- ⁵ Xu, K.; von Cresce, A. *J. Mater. Chem.*, **2011**, *21*, 9849.
- ⁶ Goodenough, J.B.; Park, K.S. *J. Am. Chem. Soc.* **2013**, *135*, 1167
- ⁷ Van der Ven, A.; Bhattacharya, J.; Belak, A.A. *Acc. Chem. Res.* **2013**, *46(5)*, 1216
- ⁸ Flandrois, D.; Simon, B. *Carbon*, **1999**, *37*, 165.
- ⁹ Aurbach, D.; Markovsky, B.; Weissman, I.; Levi, E.; Ein-Eli, Y. *Electrochim. Acta*, **1999**, *45*, 67.
- ¹⁰ Endo, M.; Kim, C.; Nishimura, K.; Fujino, J.; Miyashita, K. *Carbon*, **2000**, *38*, 183.
- ¹¹ Zheng, T.; Sue, J.; Dahn, J.R. *Chem. Mater.*, **1996**, *8*, 389.
- ¹² Fong, R.; von Sacken, u.; Dahn, J.R. *J. Electrochem. Soc.* **1990**, *137*, 2009.
- ¹³ Lee, K.T.; Jeong, S.; Cho, J. *Acc. Chem. Res.* **2013**, *46(5)*, 1161
- ¹⁴ Guilnard, M.; Croguennec, L.; Denux, D.; Delmas, C. *Chem. Mater.* **2003**, *15*, 4476
- ¹⁵ Delmas, C.; Croguennec, L. *Mater. Res. Soc. Bulletin* **2002**, *27*, 608
- ¹⁶ Ohzuku T., Makimura Y., *Chem. Lett.* **2001**, *7*, 642
- ¹⁷ Ohzuku T., Makimura Y., *Chem. Lett.* **2001**, *8*, 744
- ¹⁸ Sun, Y.-K.; Chen, Z.; Noh, H.-J.; Lee, D.-J.; Jung, H.-G.; Ren, Y.; Wang, S.; Yoon, C. S.; Myung, S.-T.; Amine, K. *Nat. Mater.* **2012**, *11*, 941
- ¹⁹ Myung, S.-T.; Noh, H.-J.; Yoon, S.-J.; Lee, E.-J.; Sun, Y.-K. *J. Phys. Chem. Lett.* **2014**, *5*, 671
- ²⁰ Thackeray, M. M.; Kang, S.-H.; Johnson, C. S.; Vaughey, J. T.; Benedek, R.; Hackney, S. A. *J. Mater Chem.* **2007**, *17*, 3112
- ²¹ Zhou, F.; Zhao, X.; Van Bommel, A.; Xia, X.; Dahn, J. R. *J. Electrochem. Soc.* **2011**, *158*, A187
- ²² Croy, J.A.; Abouimrane, A.; Zhang, Z., *MRS Bulletin* **2014**, *39*, 407
- ²³ Thackeray, M. M.; Johnson, C. S.; Vaughey, J. T.; Li, N.; Hackney, S. A. *J. Mater. Chem.* **2005**, *15*, 2257
- ²⁴ Thackeray, M. M.; Kang, S.-H.; Johnson, C. S.; Vaughey, J. T.; Hackney, S. A. *Electrochem. Commun.* **2006**, *8*, 1531
- ²⁵ Yu, H.; Ishikawa, R.; So, Y.-G.; Shibata, N.; Kudo, T.; Zhou, H.; Ikuhara, Y. *Angew. Chem. Int. Ed.* **2013**, *52*, 5969
- ²⁶ Lu, Z.; Chen, Z.; Dahn, J. R. *Chem. Mater.* **2003**, *15*, 3214-3220.
- ²⁷ Lei, C.H.; Barenò, J.; Wen, J.G.; Petrov, I.; Kang, S.-H.; Abraham, D.P. *J. Power Sources* **2008**, *178*, 422-433.
- ²⁸ Wen, J.G.; Barenò, J.; Lei, C.H.; Kang, S.H.; Balasubramanian, M.; Petrov, I.; Abraham, D.P. *Solid State Ionics* **2011**, *182*, 98
- ²⁹ Jarvis, K. A.; Deng, Z.; Allard, L. F.; Manthiram, A.; Ferreira, P. J. *Chem. Mater.* **2011**, *23(16)*, 3614
- ³⁰ Barenò, J.; Balasubramanian, M.; Kang, S. H.; Wen, J. G.; Lei, C. H.; Pol, S. V.; Petrov, I.; Abraham, D. P. *Chem. Mater.* **2011**, *23*, 2039
- ³¹ Koga, H.; Croguennec, L.; Mannesiez, Ph.; Ménétrier, M.; Weill, F.; Bourgeois, L.; Duttine, M.; Suard, E.; Delmas, C. *J. Phys. Chem. C* **2012**, *116*, 13497
- ³² McCalla, E.; Rowe, A. W.; Shunmugasundaram, R.; Dahn, J. R. *Chem. Mater.* **2013**, *25*, 989
- ³³ McCalla, E.; Rowe, A. W.; Brown, C. R.; Hacquebard, P.; Dahn, J. R. *J. Electrochem. Soc.* **2013**, *160*, A1134
- ³⁴ McCalla, E.; Lowartz, C. M.; Brown, C. R.; Dahn, J. R. *Chem. Mater.* **2013**, *25*, 912
- ³⁵ McCalla, E.; Li, J.; Rowe, A. W.; Dahn, J. R. *J. Electrochem. Soc.*, **2014**, *161(4)*, A606
- ³⁶ Long, B.R.; Croy, J.R.; Dogan, F.; Suchomel, M.R.; Key, B.; Wen, J.; Miller, D.J.; Thackeray, M.M.; Balasubramanian, M. *Chem. Mater.* **2014**, *26*, 3565
- ³⁷ Weill, F.; Tran, N.; Croguennec, L.; Delmas, C. *J. Power Sources* **2007**, *172*, 893
- ³⁸ Lee, J.; Urban, A.; Li, X.; Su, D.; Hautier, G.; Ceder, C. *Science* **2014**, *343*, 519
- ³⁹ Lu, Z.; Dahn, J. R. *Electrochem. Solid-State Lett.* **2001**, *4*, A191.
- ⁴⁰ Armstrong, A.R.; Holzapfel, M.; Novàk, P.; Johnson, C.S.; Kang, S.-H.; Thackeray, M.M.; Bruce, P.G. *J. Am. Chem. Soc.* **2006**, *128*, 8694.
- ⁴¹ Koga, H.; Croguennec, L.; Ménétrier, M.; Douhil, K.; Belin, S.; Bourgeois, L.; Suard, E.; Weill, F.; Delmas, C. *J. Electrochem. Soc.* **2013**, *160(6)*, A786

- 1
2
3
4⁴² Sathiya, M.; Ramesha, K.; Rousse, G.; Foix, D.; Gonbeau, D.; Prakash, A. S.; Doublet, M. L.;
5 Hemalatha, K.; Tarascon, J.-M. *Chem. Mater.* **2013**, *25*, 1121
- 6⁴³ Sathiya, M.; Rousse, G.; Ramesha, K.; Laisa, C. P.; Vezin, H.; Sougrati, M. L.; Doublet, M. L.; Foix,
7 D.; Gonbeau, D.; Walker, W.; Prakash, A. S.; Ben Hassine, M.; Dupont, L.; Tarascon, J.-M. *Nat. Mater.*
8 **2013**, *12*, 827
- 9⁴⁴ Boulineau A.; Simonin L.; Colin J.- F.; Canevet E.; Daniel L.; Patoux S. *Chem. Mater.* **2012**, *24* (18) 3558
- 10⁴⁵ Boulineau, A.; Simonin, L.; Colin, J.F.; Bourbon, C.; Patoux, S. *Nano Lett.*, **2013**, *13*, 3857
- 11⁴⁶ Koga, H.; Croguennec, L.; Ménétrier, M.; Mannesiez, P.; Weill, F.; Delmas, C. *J. Power Sources* **2013**,
12 *236*, 250
- 13⁴⁷ Genevois, C.; Koga, H.; Croguennec, L.; Ménétrier, M.; Delmas, C.; Weill, F. *J. Phys. Chem. C* DOI:
14 10.1021/jp509388j
- 15⁴⁸ Sathiya, M.; Abakumov, A. M.; Foix, D.; Rousse, G.; Ramesha, K.; Saubanère, M.; Doublet, M. L.;
16 Vezin, H.; Laisa, C. P.; Prakash, A. S.; Gonbeau, D.; van Tendeloo, G.; Tarascon, J.-M. *Nat. Mater.*
17 DOI:10.1038/NMAT4137
- 18⁴⁹ Croy, J.A.; Gallagher, K.G.; Balasubramanian, M.; Chen, Z.; Ren, Y.; Kim, D.; Kang, S.-H.; Dees, D.W.;
19 Thackeray, M.M. *J. Phys. Chem. C* **2013**, *117*, 6525
- 20⁵⁰ Gallagher, K.G.; Croy, J.R.; Balasubramanian, M.; Bettge, M.; Abraham, D.P.; Burell, A.K.; Thackeray,
21 M.M. *Electrochem. Comm.* **2013**, *33*, 96-98
- 22⁵¹ Croy, J.R.; Gallagher, K.G.; Balasubramanian, M.; Long, B.R.; Thackeray, M.M. *J. Electrochem. Soc.*
23 **2014**, *161*(3), A318
- 24⁵² Lee, E.; Koritala, R.; Miller, D.J.; Johnson, C.S. *J. Electrochem. Soc.*, **2015**, *162*(3), A322
- 25⁵³ Tarascon, J.M.; Sathiya, M.; Ramesha, K.; Abakumov, A.M.; Rousse, G.; Gonbeau, D.; Doublet, M.L.;
26 Prakash, A.S.; Van Tendeloo G. The 17th International Meeting on Lithium Batteries, June 10-14, 2014,
27 Como, Italy, Abstract MA2014-01-103
- 28⁵⁴ Laha, S.; Moran, E.; Saez-Puche, R.; Alario-Franco, M. A.; Dos santos-Garcia, A.J.; Gonzalo, E.; Kuhn, A.;
29 Natarajan, S.; Gopalakrishnan, J.; Garcia-Alvarado, F. *J. Mater. Chem. A*, **2013**, *1*, 10686
- 30⁵⁵ Liu, J.; Reeja-Jayan, B.; Manthiram, A. *J. Phys. Chem. C*, **2010**, *114*, 9528
- 31⁵⁶ Bettge, M.; Li, Y.; Sankaran, B.; Dietz Rago, N.; Spila, T.; Haasch, R.T.; Petrov, I.; Abraham, D.P. *J.*
32 *Power Sources* **2013**, *233*, 346
- 33⁵⁷ Pol, V.G.; Li, Y.; Dogan, F.; Secor, E.; Thackeray, M.M.; Abraham, D.P. *J. Power Sources* **2014**, *258*, 46
- 34⁵⁸ Yang, Z.; Choi, D.; Kerisit, S.; Rosso, K.; Wang, D.; Zhang, J.; Graff, G.; Liu, J. *J. Power Sources*, **2009**,
35 *192*, 588.
- 36⁵⁹ Chen, Z.; Belharouak, I.; Sun, Y.K.; Amine, K. *Adv. Funct. Mater.* **2013**, *23*, 959.
- 37⁶⁰ Froschl, T.; Hormann, U.; Kubiak, P.; Kucerova, G.; Pfanzelt, M.; Weiss, C.; Behm, R.; Husig, N.; Kaiser,
38 U.; Lfester, K.; Wohlfahrt-Mehrens, M. *Chem. Soc. Rev.*, **2012**, *41*, 5313.
- 39⁶¹ Reddy, M.V.; Rao, G.V.S.; Chowdari, B.V.R. *Chem. Rev.* **2013**, *113*, 5364.
- 40⁶² Ohzuku, T.; Ueda, A.; Yamamoto, N. *J. Electrochem. Soc.* **1995**, *142*, 1431.
- 41⁶³ Wagemaker, M.; Mulder, F.M. *Acc. Chem. Res.* **2013**, *46*(5), 1206
- 42⁶⁴ Song, M.; Benayad, A.; Choi, Y.; Park, K., *Chem. Commun.* **2012**, *48*, 516.
- 43⁶⁵ Kim, C.; Norberg, N.; Alexer, C.; Kostecki, R.; Cabana, J. *Adv. Funct. Mater.* **2013**, *23*, 1214.
- 44⁶⁶ Dominko, R.; Baudrin, E.; Umek, P.; Arcon, D.; Gaberscek, M.; Jamnik, J. *Electrochem. Commun.*, **2006**,
45 *8*, 673.
- 46⁶⁷ Brutti, S.; Gentili, V.; Menard, H.; Scrosati, B.; Bruce, P.G. *Adv. Energy Mater.* **2012**, *2*, 322.
- 47⁶⁸ Fehse, M.; Fischer, F.; Tessier, C.; Stievano, L.; Monconduit, L. *J. Power Sources*, **2013**, *231*, 23.
- 48⁶⁹ Belharouak, I.; Konig, G.M. Jr.; Tan, T.; Yumoto, H.; Ota, N.; Amine, K. *J. Electrochem. Soc.*, **2012**, *159*,
49 A1165.
- 50⁷⁰ He, Y.B.; Li, B.; Liu, M.; Zhang, C.; Lu, W.; Yang, C.; Li, J.; Du, H.; Zhang, B.; Yang, Q.Y.; Kim, J.K.; Kang, F.
51 *Sci. Rep.*, **2012**, *2*, 913.
- 52⁷¹ Bernhard, R.; Meini, S.; Gasteiger, H.A. *J. Electrochem. Soc.* **2014**, *161*, A497.
- 53⁷² Thackeray, M.M.; David, W.I.F.; Bruce, P.G.; Goodenough, J.B. *Mater. Res. Bull.* **1983**, *18*, 461
- 54⁷³ G. Amatucci, J.M. Tarascon, *J. Electrochem. Soc.* **2002**, *149*, K31.
- 55⁷⁴ Hu, M.; Pang, X.; Zhou, Z. *J. Power Sources* **2013**, *237*, 229
- 56⁷⁵ Manthiram, A.; Chemelewski, K.; Lee, E.-S. *Energy Environ. Sci.* **2014**, *7*, 1339
- 57⁷⁶ Patoux, S.; Daniel, L.; Bourbon, C.; Lignier, H.; Pagano, C.; Le Cras, F.; Jouanneau, S.; Martinet, S. *J.*
58 *Power Sources*, **2009**, *189*, 344
- 59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- ⁷⁷ Zhang, Z.; Hu, L.; Wu, H.; Weng, W.; Koh, M.; Redfern, P.; Curtiss, L.A.; Amine, K. *Energy Environ. Sci.* **2013**, *6*, 1806
- ⁷⁸ Hu, L.; Zhang, Z.; Amine, K. *Electrochem. Commun.* **2013**, *35*, 76
- ⁷⁹ Markevich, E.; Salitra, G.; Fridman, K.; Sharabi, R.; Gershinsky, G.; Garsuch, A.; Semrau, G.; Schmidt, M.A.; Aurbach, D. *Langmuir* **2014**, *30*, 7414
- ⁸⁰ Bouayad, H.; Wang, Z.; Dupré, N.; Dedryvère, R.; Foix, D.; Franger, S.; Martin, J.-F.; Boutafa, L.; Patoux, S.; Gonbeau, D.; Guyomard, D. *J. Phys. Chem. C*, **2014**, *118*, 4634
- ⁸¹ Padhi, A. K.; Nanjundaswamy, K. S.; Goodenough, J.B.; *J. Electrochem. Soc.* **1997**, *144*(4), 1188
- ⁸² Masquelier, C.; Croguennec, L. *Chem. Rev.*, **2013**, *113*(8), 6552
- ⁸³ Malik, R.; Abdellahi, A.; Ceder, G. *J. Electrochem. Soc.*, **2013**, *160*(5), A3197
- ⁸⁴ Ravet, N.; Chouinard, Y.; Magnan, J.F.; Besner, S.; Gauthier, M.; Armand, M. *J. Power Sources*, **2001**, *97-98*, 503
- ⁸⁵ Yamada, A.; Koizumi, H.; Nishimura, S. I.; Sonoyama, N.; Kanno, R.; Yonemura, M.; Nakamura, T.; Kobayashi, Y. *Nat. Mater.* **2006**, *5*(5), 357
- ⁸⁶ Meethong, N.; Huang, H.Y.S.; Speakman, S.A.; Carter, W.C.; Chiang, Y.M. *Adv. Funct. Mater.*, **2007**, *17*(7), 1115
- ⁸⁷ Wagemaker, M.; Mulder, F.M.; van der Ven, A. *Adv. Mater.*, **2009**, *21*, 1
- ⁸⁸ Van der Ven, A.; Garikipati, K.; Kim, S.; Wagemaker, M. *J. Electrochem. Soc.*, **2009**, *156*(11), A949
- ⁸⁹ Van der Ven, A.; Wagemaker, M. *Electrochem. Commun.*, **2009**, *11*(4), 881
- ⁹⁰ Lee, K.T.; Kan, W.H.; Nazar, L.F. *J. Am. Chem. Soc.* **2009**, *131*, 6044
- ⁹¹ Orikasa, Y.; Maeda, T.; Koyama, Y.; Murayama, H.; Fukuda, K.; Tanida, H.; Arai, H.; Matsubara, E.; Uchimoto, Y.; Ogumi, Z.; *J. Am. Chem. Soc.*, **2013**, *135*, 5497
- ⁹² Sasaki, T.; Ukyo, Y.; Novák, P., *Nature Mater.* **2013**, *12*, 569.
- ⁹³ Zhang, X.; van Hulzen, M.; Singh, D.P.; Brownrigg, A.; Wright, J.P.; van Dijk, N.H.; Wagemaker, M., *Nano Lett.*, **2014**, *14*, 2279
- ⁹⁴ Liu, H.; Strohbridge, F.C.; Borkiewicz, O.J.; Wiaderek, K.M.; Chapman, K.W.; Chupas, P.J.; Grey, C.P. *Science*, **2014**, *344*, 1252817-1
- ⁹⁵ Malik, R.; Zhou, F.; Ceder, G. *Natur. Mater.*, **2011**, *10*, 587
- ⁹⁶ Delacourt, C.; Poizot, P.; Tarascon, J. M.; Masquelier, C. *Nat. Mater.* **2005**, *4*, 254
- ⁹⁷ Boucher, F.; Gaubicher, J.; Cuisinier, M.; Guyomard, D.; Moreau P. *J. Am. Chem. Soc.* **2014**, *136*, 9144.
- ⁹⁸ Leriche, J. B.; Hamelet, S.; Shu, J.; Morcrette, M.; Masquelier, C.; Ouvrard, G.; Zerrouki, M.; Soudan, P.; Belin, S.; Elkaim, E.; Baudalet, F. *J. Electrochem. Soc.*, **2010**, *157*, A606
- ⁹⁹ Godbole, V. A.; Hess, M.; Villevieille, C.; Kaiser, H.; Colin, J. F.; Novak, P. *RSC Advances*, **2013**, *3*, 757
- ¹⁰⁰ Bianchini, M.; Leriche, J. B.; Laborier, J.-L.; Gendrin, L.; Suard, E.; Croguennec L.; Masquelier, C. *J. Electrochem. Soc.*, **2013**, *160*, A2176
- ¹⁰¹ Roberts, M.; Biendicho, J. J.; Hull, S.; Beran, P.; Gustafsson, T.; Svensson, G.; Edstrom K., *J. Power Sources*, **2013**, *226*, 249
- ¹⁰² Ramar, V.; Saravanan, K.; Gajjela, S.R.; Hariharan, S.; Balaya, P. *Electrochim. Acta*, **2013**, *105*, 496
- ¹⁰³ Yamada, A.; Hosoya, M.; Chung, S.-C.; Kudo, Y.; Hinokuma, K.; Liu, K.-Y.; Nishi, Y. *J. Power Sources* **2003**, *119-121*, 232
- ¹⁰⁴ Ravnsbæk, D. B.; Xiang, K.; Xing, W.; Borkiewicz, O. J.; Wiaderek, K. M.; Gionet, P.; Chapman, K. W.; Chupas, P. J.; Chiang, Y.-M. *Nano Lett.* **2014**, *14*, 1484
- ¹⁰⁵ Omenya, F.; Chernova, N.A.; Zhang, R.; Fang, J.; Huang, Y.; Cohen, F.; Dobrzynski, N.; Senanayake, S.; Xu, W.; Whittingham, M.S. *Chem. Mater.* **2013**, *25*, 85
- ¹⁰⁶ Rui, X.; Yan, Q.; Skyllas-Kazacos, M.; Lim, T.M. *J. Power Sources*, **2014**, *258*, 19
- ¹⁰⁷ Hautier, G.; Jain, A.; Mueller, T.; Moore, C.; Ong, S.O.; Ceder, G. *Chem. Mater.* **2013**, *25*, 2064
- ¹⁰⁸ Rouse, G.; Tarascon, J.M. *Chem. Mater.* **2014**, *26*, 394.
- ¹⁰⁹ Tripathi, R.; Ramesh, T. N.; Ellis, B. L.; Nazar, L. F. *Angew. Chem., Int. Ed.*, **2010**, *49*, 8738
- ¹¹⁰ Tripathi, R.; Popov, G.; Ellis, B. L.; Huq, A.; Nazar, L. F., *Energy Environ. Sci.*, **2012**, *5*, 6238
- ¹¹¹ Tripathi, R.; Popov, G.; Sun, X.; Ryan, D.H.; Nazar, L.F. *J. Mater Chem. A*, **2013**, *1*, 2990
- ¹¹² Lander, L.; Reynaud, M.; Rouse, G.; Sougrati, M.T.; Laberty-Robert, C.; Messinger, R.J., Deschamps, M.; Tarascon, J.M. *Chem. Mater.* **2014**, *26*, 4178
- ¹¹³ Sobkowiak, A.; Roberts, M. R.; Younesi, R.; Ericsson, T.; Häggström, L.; Tai, C.-W.; Andersson, A. M.; Edstrom, K.; Gustafsson, T.; Björefors, F. *Chem. Mater.* **2013**, *25*(15), 3020

- 1
2
3
4 ¹¹⁴ Nanjundaswamy, K.S.; Padhi, A.K.; Goodenough, J.B.; Okada, S.; Ohtsuka, H.; Arai, H.; Yamaki, J. *Solid State Ionics* **1996**, *92*, 1.
- 5
6 ¹¹⁵ Padhi, A.K.; Nanjundaswamy, K.S.; Masquelier, C.; Goodenough, J.B. *J. Electrochem. Soc.* **1997**, *144*, 2581.
- 7
8 ¹¹⁶ Ben Yahia, M.; Lemoigno, F.; Rousse, G.; Boucher, F.; Tarascon, J. M.; Doublet, M. L. *Energy Environ. Sci.* **2012**, *5* (11), 9584
- 9
10 ¹¹⁷ Ye, T.; Barpanda, P.; Nishimura, S.; Furuta, N.; Chung, S.-C.; Yamada, A. *Chem. Mater.* **2013**, *25*, 3623
- 11 ¹¹⁸ Yamada, A.; Iwane, N.; Harada, Y.; Nishimura, S.; Koyama, Y.; Tanaka, I. *Adv. Mater.*, **2010**, *22*, 3583
- 12 ¹¹⁹ Armstrong, A.R.; Kuganathan, N.; Islam, M.S.; Bruce, P.G. *J. Am. Chem. Soc.*, **2011**, *133*, 13031
- 13 ¹²⁰ Ateba Mba, J.-M.; Masquelier, C.; Suard E.; Croguennec, L. *Chem. Mater.* **2012**, *24*, 1223.
- 14 ¹²¹ Bianchini, M.; Ateba-Mba, J. M.; Dagault, P.; Bogdan, E.; Carlier, D.; Suard, E.; Masquelier C.; Croguennec, L. *J. Mater. Chem. A* **2014**, *26*, 10182
- 15 ¹²² Harrison, K.L.; Bridges, C.A.; Segre, C.U.; Varnado, C.D.; Applestone, D.; Bielawski, C.W.; Paranthaman, M.P.; Manthiram, A. *Chem. Mater.* **2014**, *26*, 3849.
- 16 ¹²³ Chen, Z.; Chen, Q.; Chen, L.; Zhang, R.; Zhou, H.; Chernova, N.A.; Whittingham, M.S. *J. Electrochem. Soc.* **2013**, *160* (10), A1777
- 17 ¹²⁴ Chen, Z.; Chen, Q.; Wang, H.; Zhang, R.; Zhou, H.; Chen, L.; Whittingham, M.S. *Electrochem. Comm.* **2014**, *46*, 67
- 18 ¹²⁵ West, A.R.; Glasser, F.P. *J. Solid State Chem.* **1972**, *4*, 20
- 19 ¹²⁶ Islam, M.S.; Dominko, R.; Masquelier, C.; Sirisopanaporn, C.; Armstrong, A.R.; Bruce, P.G. *J. Mater. Chem.* **2011**, *21*, 9811
- 20 ¹²⁷ Armstrong, A.R.; Sirisopanaporn, C.; Adamson, P.; Billaud, J.; Dominko, R.; Masquelier, C.; Bruce, P.G. *Z. Anorg. Allg. Chem.* **2014**, *640*(6), 1043
- 21 ¹²⁸ Peng, G.; Zhang, L.L.; Yang, X.L.; Duan, S.; Liang, G.; Huang, Y.H. *J. Alloys Compd.* **2013**, *570*, 1
- 22 ¹²⁹ Singh, S.; Mitra, S. *Electrochim. Acta*, **2014**, *123*, 378
- 23 ¹³⁰ He, G.; Manthiram, A. *Adv. Funct. Mater.* **2014**, *33*, 5277
- 24 ¹³¹ Gummow, R.J.; He, Y. *J. Power Sources*, **2014**, *253*, 315
- 25 ¹³² Legagneur, V.; An, Y.; Mosbah, A.; Portal, R.; Le Gal La Salle, A.; Verbaere, A.; Guyomard, D.; Piffard, Y. *Solid State Ionics*, **2001**, *139*, 37
- 26 ¹³³ Yamada, A.; Iwane, N.; Harada, Y.; Nishimura, S.-i.; Koyama, Y.; Tanaka, I. *Adv. Mater*, **2010**, *22*, 3583
- 27 ¹³⁴ Yamashita, Y.; Barpanda, P.; Yamada, Y.; Yamada, A. *ECS Electrochem. Lett.* **2013**, *2*(8), A75
- 28 ¹³⁵ Kim, J.C.; Moore, C.; Kang, B.; Hautier, G.; Jain, A.; Ceder, G. *J. Electrochem. Soc.* **2011**, *158*(3), A309
- 29 ¹³⁶ Yamada, A.; Iwane, N.; Nishimura, S.C.; Koyama, Y.; Tanaka, I. *J. Mater. Chem.* **2011**, *21*(29), 10690
- 30 ¹³⁷ Tao, L.; Rousse, G.; Chotard, J.N.; Dupont, L.; Bruyère, S.; Hanžel, D.; Mali, G.; Dominko, R.; Levasseur, S.; Masquelier, C. *J. Mater. Chem. A* **2014**, *2*, 2060
- 31 ¹³⁸ Li, S.; Xu, L.; Li, G.; Wang, M.; Zhai, Y. *J. Power Sources*, **2013**, *236*, 54
- 32 ¹³⁹ Afyon, S.; Mensing, C.; Krumeich, F.; Nesper, R. *Solid State Ionics*, **2014**, *256*, 103
- 33 ¹⁴⁰ Kim, J. C.; Seo, D. H.; Li, X.; Ceder G. <https://ecs.confex.com/ecs/226/webprogram/Paper38372.html>
- 34 ¹⁴¹ Larcher, D.; Tarascon, J.M.; *Nature* **2014**, *7*, 19.
- 35 ¹⁴² Recham, N.; Armand, M.; Laffont, L.; Tarascon, J.-M. *Electrochem. Solid-State Lett.* **2009**, *12*, A39.
- 36 ¹⁴³ Recham, N.; Dupont, L.; Courty, M.; Djellab, K.; Larcher, D.; Armand, M.; Tarascon, J.-M. *Chem. Mater.* **2009**, *21*, 1096.
- 37 ¹⁴⁴ Tarascon, J. M.; Recham, N.; Armand, M.; Chotard, J. N.; Barpanda, P.; Walker, W.; Dupont, L. *Chem. Mater.* **2010**, *22*, 724.
- 38 ¹⁴⁵ Eames, C.; Clark, J.M.; Rousse, G.; Tarascon, J.-M.; Islam, S. *Chem. Mater.* **2014**, *26*, 3672
- 39 ¹⁴⁶ Clark, J.M.; Eames, C.; Reynaud, M.; Rousse, G.; Chotard, J.M.; Tarascon, J.-M.; Islam, M.S. *J. Mater. Chem. A*, **2014**, *2*, 7446
- 40 ¹⁴⁷ Matts, I.; Chen, H.; Ceder, G. *ECS Electrochem. Lett.* **2013**, *2*(8), A81
- 41 ¹⁴⁸ Melot, B.C.; Tarascon, J.M. *Acc. Chem. Res.* **2013**, *46*, 1226.
- 42 ¹⁴⁹ Dey, A. N. *J. Electrochem. Soc.* **1971**, *118*, 1547.
- 43 ¹⁵⁰ Poizot, P.; Laruelle, S.; Grugeon, S.; Dupont L.; Tarascon, J.M. *Nature* **2000**, *407*, 496.
- 44 ¹⁵¹ Godshall, N.A.; Raistrick, I.D.; Huggins, R.A. *Mat. Res. Bull.* **1980**, *15*, 561.
- 45 ¹⁵² Palacin, M.R. *Chem. Soc. Rev.* **2009**, *38*, 2565.
- 46 ¹⁵³ Zhang, W.J. *J. Power Sources*, **2011**, *196*, 13.
- 47 ¹⁵⁴ Zhang, W.J. *J. Power Sources*, **2011**, *196*, 877.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- ¹⁵⁵ Larcher, D.; Beattie, S.; Morcrette, M.; Edstrom, K.; Jumas, J.C.; Tarascon, J.M. *J. Mater. Chem.* **2007**, *17*, 3759
- ¹⁵⁶ Cho, J. *J. Mater. Chem.*, **2010**, *20*, 4009.
- ¹⁵⁷ Obrovac, M.N.; Krause, L.J. *J. Electrochem. Soc.*, **2007**, *154*, A103.
- ¹⁵⁸ Yang, M.J.; Winter, M.; Besenhard, J.O.S. *Solid State Ionics*, **1996**, *90*, 281.
- ¹⁵⁹ Yang, J.; Takeda, Y.; Imanishi, M.; Yamamoto, O. *J. Electrochem. Soc.*, **1999**, *146*, 4009.
- ¹⁶⁰ Johnson, C.S.; Vaughey, J.T.; Thackeray, M.; Sarakonsri, T.; Hackney, S.A.; Fransson, L.; Edstrom, K.; Thomas, J.O. *Electrochem. Commun.*, **2000**, *2*, 595.
- ¹⁶¹ Al-Maghrabi, M.A.; Thorne, J.S.; Sanderson, R.J.; Byers, J.N.; Dahn, J.R.; Dunlap, R.A. *J. Electrochem. Soc.*, **2012**, *159*, A711.
- ¹⁶² Smith, A.J.; Burns, J.C.; Trussler, S.; Dahn, J.R. *J. Electrochem. Soc.* **2010**, *157*, A196.
- ¹⁶³ Liu, Bo.; Abouimrane, A.; Ren, Y.; Neufeind, J.; Fang, Z.Z.; Amine, K. *J. Electrochem. Soc.* **2013**, *160*, A882.
- ¹⁶⁴ Philippe, B.; Dedryvere, R.; Allouche, J.; Lindgren, F.; Gorgoi, M.; Rensmo, H.; Gonbeau, D.; Edstrom, K. *Chem. Mater.* **2012**, *24*, 1107.
- ¹⁶⁵ Philippe, B.; Dedryvere, R.; Gorgoi, M.; Rensmo, H.; Gonbeau, D.; Edstrom, K. *Chem. Mater.* **2013**, *25*, 394.
- ¹⁶⁶ Oumellal, Y.; Delpuech, N.; Mazouzi, D.; Dupre, N.; Gaubicher, J.; Moreau, P.; Soudan, P.; Lestriez, B.; Guyomard, D. *J. Mater. Chem.* **2011**, *21*, 6201.
- ¹⁶⁷ Wachtler, M.; Besenhard, J.O.; Winter, M. *J. Power Sources* **2001**, *94*, 189.
- ¹⁶⁸ Ulldemolins, M.; Le Cras, F.; Pecquenard, B.; Phan, V.P.; Martin, L.; Martinez, H. *J. Power Sources* **2012**, *206*, 245.
- ¹⁶⁹ Wang, C.; Wu, H.; Chen, Z.; Mc Dowell, M.T.; Cui, Y.; Bao, Z. *Nat. Chem.* **2013**, *5*, 1042.
- ¹⁷⁰ Li, J.; Lewis R.B.; Dahn, J.R. *Electrochem. Solid-State. Lett.* **2007**, *10*, A17.
- ¹⁷¹ Lestriez, B.; Bahri, S.; Su, I.; Roue, L.; Guyomard, D. *Electrochem. Commun.* **2007**, *9*, 2801.
- ¹⁷² Hochgatterer, N.; Schweiger, M.; Koller, S.; Rainmann, P.; Wohrle, T.; Wurm, C.; Winter, M. *Electrochem. Solid-State Lett.* **2008**, *11*, A76.
- ¹⁷³ Bridel, J.S.; Azais, T.; Morcrette, M.; Tarascon, J.M.; Larcher, D. *J. Electrochem. Soc.* **2011**, *158*, A750.
- ¹⁷⁴ Bridel, J.S.; Azais, T.; Morcrette, M.; Tarascon, J.M.; Larcher, D. *Chem. Mater.* **2010**, *22*, 1229.
- ¹⁷⁵ Kovalenko, I.; Zdyro, B.; Magasinski, A.; Hertzberg, B.; Milicev, Z.; Burtovy, R.; Yushin, G. *Science*, **2011**, *334*, 75.
- ¹⁷⁶ Erk, C.; Brexneski, T.; Sommer, H.; Schneider, R.; Janek, J. *Appl. Mater. Interfaces* **2013**, *5*, 7299.
- ¹⁷⁷ Wu, M.; Xiao, X.; Vukmirovic, N.; Xun, S.; Prodip, K.D.; Song, X.; Olalde-Velasco, P.; Wang, D.; Weber, A.Z.; Wang, L.W.; Battaglia, V.S.; Yang, W.; Liu, G. *J. Am. Chem. Soc.* **2013**, *135*, 12048.
- ¹⁷⁸ Wang, C.; Wu, H.; Chen, Z.; Mc Dowell, M.; Cui, Y.; Bao, Z. *Nat. Chem.* **2013**, *5*, 1042.
- ¹⁷⁹ Toudjine, A.; Morcrette, M.; Courty, M.; Davoisne, C.; Lejeune, M.; Mariage, N.; Porchez, W.; Larcher, D. (*In preparation*)
- ¹⁸⁰ Cabana, J.; Monconduit, L.; Larcher, D.; Palacin, M.R. *Adv. Mater.* **2010**, *22*, E170
- ¹⁸¹ Gregorczyk, K.E.; Liu, Y.; Sullivan, J.P.; Rubloff, G.W. *ACS Nano* **2013**, *7*, 6354.
- ¹⁸² Balaya, P.; Li, H.; Kienle, L.; Maier, J. *Adv. Funct. Mater.*, **2003**, *13*, 621.
- ¹⁸³ Zhukovskii, Y.F.; Kotomin, E.A.; Balaya, P.; Maier, J. *Solid State Sci.* **2008**, *10*, 491.
- ¹⁸⁴ Laruelle, S.; Grugeon, S.; Poizot, P.; Dolle, M.; Dupont, L.; Tarascon, J.M. *J. Electrochem. Soc.* **2002**, *149*, A627.
- ¹⁸⁵ Gachot, G.; Grugeon, S.; Armand, M.; Pilard, S.; Guenot, P.; Tarascon, J.M.; Laruelle, S. *J. Power Sources*, **2008**, *178*, 409.
- ¹⁸⁶ Ponrouch, A.; Taberna, P.L.; Simon, P.; Palacin, M.R. *Electrochim. Acta* **2012**, *61*, 13.
- ¹⁸⁷ Hu, Y.Y.; Liu, Z.; Nam, K.W.; Borkiewicz, O.J.; Cheng, J.; Hua, X.; Dunstan, M.T.; Yu, X.; Wiaderek, K.M.; Du, L.S.; Chapman, K.W.; Chupas, P.J.; Yang, X.Q.; Grey, C.P. *Nat. Mater.* **2013**, *12*, 1130.
- ¹⁸⁸ Gmitter, A.J.; Halajko, A.; Sideris, P.J.; Greenbaum, S.G.; Amatucci, G.G. *Electrochim. Acta.* **2013**, *88*, 735.
- ¹⁸⁹ Sauvage, F.; Tarascon, J.M.; Baudrin, E. *J. Phys. Chem. C* **2007**, *111*, 9624.
- ¹⁹⁰ Taberna, P.L.; Mitra, S.; Poizot, P.; Simon, P.; Tarascon, J.M. *Nat. Mater.* **2006**, *5*, 567.
- ¹⁹¹ Wang, F.; Yu, H.C.; Chen, M.H.; Wu, L.; Pereira, N.; Thornton, K.; Van der Ven, A.; Zhu, Y.; Amatucci, G.G.; Graetz, J. *Nature Comm.* **2012**, *3*, 1201.
- ¹⁹² Doe, R.E.; Persson, K.A.; Meng, Y.S.; Ceder, G. *Chem. Mater.* **2008**, *20*, 5274.
- ¹⁹³ Yamakawa, N.; Jiang, M.; Key, B.; Grey, C.P. *J. Am. Chem. Soc.* **2009**, *131*, 10525.

- 1
2
3
4 ¹⁹⁴ Sina, M.; Nam, K.W.; Su, D.; Pereira, N.; Yang, X.Q.; Amatucci, G.G.; Cosandey, F. *J. Mater. Chem. A*
5 **2013**, *1*, 11629.
- 6 ¹⁹⁵ Dalverny, A.L.; Filhol J.S.; Doublet, M.L. *J. Mater. Chem.* **2011**, *21*, 10134.
- 7 ¹⁹⁶ Khatib, R.; Dalverny, A.L.; Saubanere, M.; Gaberscek, M.; Doublet, M.L. *J. Phys. Chem. C* **2013**, *117*,
8 837.
- 9 ¹⁹⁷ Reddy, M.V.; Rao, G.V.S.; Chowdari, B.V.R. *Chem. Rev.* **2013**, *113*, 5364.
- 10 ¹⁹⁸ Doublet, M.L.; Lemoigno, F.; Gillot, F.; Monconduit, L. *Chem. Mater.* **2002**, *14*, 4126.
- 11 ¹⁹⁹ Oumellal, Y.; Rougier, A.; Nazri, G.A.; Tarascon, J.M.; Aymard, L. *Nat. Mater.*, **2008**, *7*, 916.
- 12 ²⁰⁰ Brutti, S.; Mulas, G.; Piciollo, E.; Panero, S.; Reale, P. *J. Mater. Chem.* **2012**, *22*, 14531.
- 13 ²⁰¹ Kasavajjula, U.; Wang, C.; Appleby, A.J. *J. Power Sources* **2007**, *163*, 1003.
- 14 ²⁰² Gershinsky, G.; Bar, E.; Monconduit, L.; Zitoun, D. *Energy Environ. Sci.* **2014**, *7*, 2012.
- 15 ²⁰³ Novak, P.; Panitz, J.-C.; Joho, F.; Lanz, M.; Imhof, R.; Coluccia, M. *J. Power Sources* **2000**, *90*, 52.
- 16 ²⁰⁴ Chandrashekar, S.; Trease, N.M.; Chang, H.J.; Du, L.S.; Grey, C.P.; Jerschow, A. *Nat. Mater.*, **2012**, *11*,
17 311.
- 18 ²⁰⁵ Ebner, M.; Marone, F.; Stampanoni, M.; Wood, V. *Science* **2013**, *342*, 716.
- 19 ²⁰⁶ Novak, P.; Goers, D.; Hardwick, L.; Holzapfel, M.; Scheifele, W.; Ufhiel, J.; Wursig, A. *J. Power Sources*
20 **2005**, *146*, 15.
- 21 ²⁰⁷ Dubarry, M.; Liaw, B.Y.; Chen, M.S.; Chyan, S.S.; Han, K.C.; Sie, W.T.; Wu, S.H. *J. Power Sources* **2011**,
22 *196*, 3420.
- 23 ²⁰⁸ Garcia, R.E.; Chiang, Y.M. *J. Electrochem Soc.* **2007**, *154*, A856.
- 24 ²⁰⁹ Ebner, M.; Chung, D.W.; Garcia, R.E.; Wood, W. *Adv. Energy Mater.* **2014**, *4*, 1301278
- 25 ²¹⁰ Ligneel, E.; Lestriez, B.; Hudhomme, A.; Guyomard, D. *J. European Ceramic Soc.*, **2009**, *29*, 925.
- 26 ²¹¹ Lestriez, B. *C. R. Chim.* **2010**, *13*, 1341.
- 27 ²¹² Zheng, H.; Li, J.; Song, X.; Liu, G.; Battaglia, V.S. *Electrochim. Acta*, **2012**, *71*, 258.
- 28 ²¹³ Zheng, H.; Zhang, L.; Liu, G.; Song, S.; Battaglia, V.S. *J. Power Sources*, **2012**, *217*, 530.
- 29 ²¹⁴ Bae, C.J.; Erdonmez, C.K.; Halloran, J.W.; Chiang, Y.M. *Adv. Mater.*, **2013**, *25*, 1254.

TOC GRAPHIC:

