



**HAL**  
open science

## High-rate electrochemical energy storage through Li<sup>+</sup> intercalation pseudocapacitance

Veronica Augustyn, Jérémy Come, Michael A. Lowe, Jong Woung Kim, Pierre-Louis Taberna, Sarah H. Tolbert, Héctor D. Abruña, Patrice Simon, Bruce Dunn

► **To cite this version:**

Veronica Augustyn, Jérémy Come, Michael A. Lowe, Jong Woung Kim, Pierre-Louis Taberna, et al.. High-rate electrochemical energy storage through Li<sup>+</sup> intercalation pseudocapacitance. *Nature Materials*, 2013, vol. 12 (n° 6), pp. 518-522. 10.1038/NMAT3601 . hal-01159902

**HAL Id: hal-01159902**

**<https://hal.science/hal-01159902v1>**

Submitted on 4 Jun 2015

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



## Open Archive TOULOUSE Archive Ouverte (OATAO)

OATAO is an open access repository that collects the work of Toulouse researchers and makes it freely available over the web where possible.

This is an author-deposited version published in : <http://oatao.univ-toulouse.fr/>  
Eprints ID : 13899

**To link to this article** : DOI:10.1038/NMAT3601  
URL : <http://dx.doi.org/10.1038/NMAT3601>

**To cite this version :**

Augustyn, Veronica and Come, Jérémy and Lowe, Michael A. and Kim, Jong Woung and Taberna, Pierre-Louis and Tolbert, Sarah H. and Abruña, Héctor D. and Simon, Patrice and Dunn, Bruce *High-rate electrochemical energy storage through Li+ intercalation pseudocapacitance*. (2013) Nature Materials, vol. 12 (n° 6). pp. 518-522. ISSN 1476-1122

Any correspondance concerning this service should be sent to the repository administrator: [staff-oatao@listes-diff.inp-toulouse.fr](mailto:staff-oatao@listes-diff.inp-toulouse.fr)

# High-rate electrochemical energy storage through Li<sup>+</sup> intercalation pseudocapacitance

Veronica Augustyn<sup>1</sup>, Jérémy Come<sup>2,3</sup>, Michael A. Lowe<sup>4</sup>, Jong Woung Kim<sup>1</sup>, Pierre-Louis Taberna<sup>2,3</sup>, Sarah H. Tolbert<sup>5</sup>, Héctor D. Abruña<sup>4</sup>, Patrice Simon<sup>2,3</sup> and Bruce Dunn<sup>1\*</sup>

**Pseudocapacitance is commonly associated with surface or near-surface reversible redox reactions, as observed with RuO<sub>2</sub> · xH<sub>2</sub>O in an acidic electrolyte. However, we recently demonstrated that a pseudocapacitive mechanism occurs when lithium ions are inserted into mesoporous and nanocrystal films of orthorhombic Nb<sub>2</sub>O<sub>5</sub> (T-Nb<sub>2</sub>O<sub>5</sub>; refs 1,2). Here, we quantify the kinetics of charge storage in T-Nb<sub>2</sub>O<sub>5</sub>: currents that vary inversely with time, charge-storage capacity that is mostly independent of rate, and redox peaks that exhibit small voltage offsets even at high rates. We also define the structural characteristics necessary for this process, termed intercalation pseudocapacitance, which are a crystalline network that offers two-dimensional transport pathways and little structural change on intercalation. The principal benefit realized from intercalation pseudocapacitance is that high levels of charge storage are achieved within short periods of time because there are no limitations from solid-state diffusion. Thick electrodes (up to 40 μm thick) prepared with T-Nb<sub>2</sub>O<sub>5</sub> offer the promise of exploiting intercalation pseudocapacitance to obtain high-rate charge-storage devices.**

Pseudocapacitance occurs whenever the charge ( $Q$ ) depends on the change in potential ( $dE$ ), yielding a capacitance ( $dQ/dE$ ) (ref. 3). The capacity can be due to monolayer adsorption of ions at an electrode surface, as in the underpotential deposition of metals<sup>4</sup>; surface redox reactions as in RuO<sub>2</sub>; or ion intercalation that does not result in a phase change. Although these redox processes are Faradaic in nature, their phenomenological behaviour, and response to experimental variables such as sweep rate, are those typical of capacitors. All of these scenarios produce a relationship between the fractional extent of charge storage,  $X$ , and the potential of the form<sup>3,5</sup>:

$$E \sim \left( \frac{RT}{nF} \right) \ln \left[ \frac{X}{(1-X)} \right] \quad (1)$$

where  $R$  is the ideal gas constant ( $\text{J mol}^{-1} \text{K}^{-1}$ ),  $T$  is the temperature (K),  $F$  is Faraday's constant ( $96,485 \text{ As mol}^{-1}$ ) and  $n$  is the number of electrons involved in the reaction. In all of these cases, a constant-current experiment yields a potential  $E$  that changes with the extent of charge  $Q$  according to:

$$Q = C \Delta E$$

where  $Q$  is the charge passed (Coulombs),  $\Delta E$  is the potential change (V) and  $C$  is the pseudocapacitance (F). This behaviour

is typical of capacitive charge/discharge, thus leading to the term pseudocapacitance<sup>3</sup>.


Of the three pseudocapacitive mechanisms mentioned above, underpotential deposition and surface redox reaction pseudocapacitance exhibit kinetics indicative of surface-controlled electrochemical processes<sup>6</sup>:

$$i = C\nu$$

where  $i$  is the current (A) and  $\nu$  is the sweep rate ( $\text{mV s}^{-1}$ ) of a cyclic voltammetry experiment. However, in intercalation pseudocapacitance, as described herein, charge storage does not occur on the surface but in the bulk material. The kinetics are not diffusion-limited and instead are limited by surface processes so that the overall behaviour seems capacitive. Intercalation pseudocapacitance is rarely observed because in most intercalation materials charge storage (even in thin films, as in anatase TiO<sub>2</sub>; refs 7,8) is limited by solid-state diffusion and therefore the peak currents scale with  $\nu^{1/2}$ .


Here we investigate the phenomenon of intercalation pseudocapacitance and the high-rate behaviour of T-Nb<sub>2</sub>O<sub>5</sub> using two different electrode techniques that provide a wide variation in sweep rates. For timescales between ~3 h and 60 s (sweep rates of 0.1–20  $\text{mV s}^{-1}$  within a voltage window of 1.2 V), we used a thin-film electrode. For shorter timescales where ohmic polarization is significant (60–500  $\text{mV s}^{-1}$ ), we used a cavity microelectrode where the active material was mixed with a conductive carbon black to alleviate the loss of electrical transport (ohmic losses)<sup>9</sup>. To confirm the small ohmic drop of this electrode, we performed cyclic voltammetry from 100–500  $\text{mV s}^{-1}$  in a bulky-ion electrolyte (Supplementary Fig. S1). In addition, we prepared thick films (~40 μm) of T-Nb<sub>2</sub>O<sub>5</sub> to determine whether the high-rate capability was limited to thin films.

Charge storage from the intercalation of lithium ions into Nb<sub>2</sub>O<sub>5</sub> can be expressed as:



where the maximum capacity is  $x = 2$  (ref. 10). Figure 1a shows cyclic voltammograms from 100 to 500  $\text{mV s}^{-1}$  in a cavity microelectrode where it is evident that both anodic and cathodic peaks are broad, about 600 mV. There is also a noticeable peak shift (and increase in peak separation  $\Delta E_p$ ) as the sweep rate increases, but the capacity remains reversible. Figure 1b presents a plot of  $\log(i)$  versus  $\log(\nu)$  from 0.1 to 500  $\text{mV s}^{-1}$  for both cathodic and anodic peaks. Assuming that the current obeys a power-law

<sup>1</sup>Department of Materials Science and Engineering, University of California, Los Angeles, California 90095, USA, <sup>2</sup>Department of Materials Science, Université Paul Sabatier, CIRIMAT UMR CNRS 5085, Toulouse 31062, France, <sup>3</sup>Réseau sur le Stockage Electrochimique de l'Energie (RS2E), FR CNRS 3459, France, <sup>4</sup>Department of Chemistry and Chemical Biology, Cornell University, Ithaca, New York 14853, USA, <sup>5</sup>Department of Chemistry and Biochemistry, University of California, Los Angeles, California 90095, USA. \*e-mail: bdunn@ucla.edu.

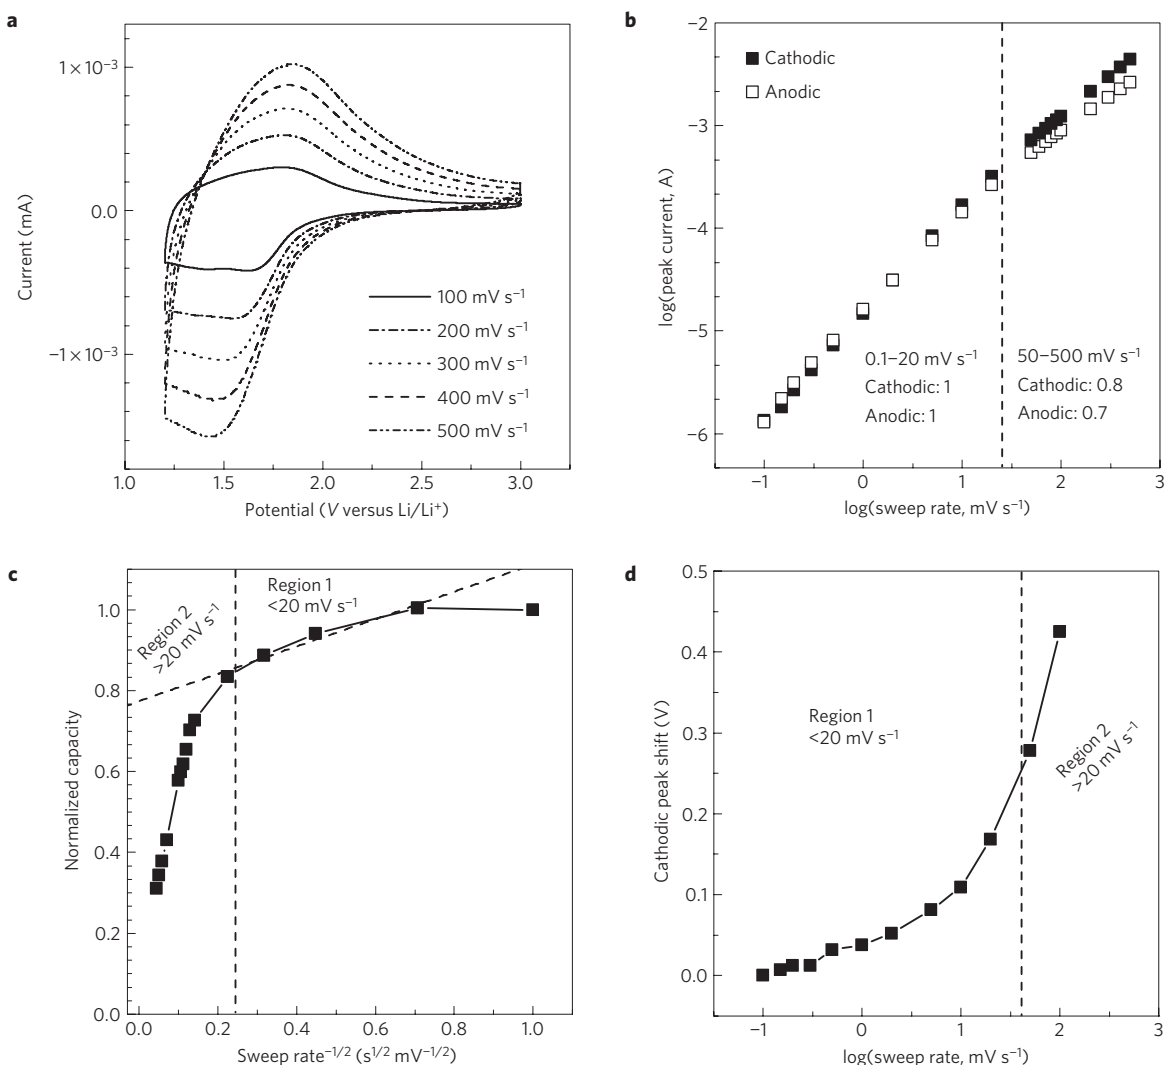


**Figure 1 | Kinetic analysis of the electrochemical behaviour of  $T\text{-Nb}_2\text{O}_5$ .** **a**, Cyclic voltammograms from 100 to 500  $\text{mV s}^{-1}$  demonstrate the high-rate capability of the material. **b**,  $b$ -value determination of the peak anodic and cathodic currents shows that this value is approximately 1 up to 50  $\text{mV s}^{-1}$ . This indicates that even at the peak currents, charge storage is capacitive. **c**, Capacity versus  $\nu^{-1/2}$  allows for the separation of diffusion-controlled capacity from capacitive-controlled capacity; two distinct kinetic regions emerge when the sweep rate is varied from 1 to 500  $\text{mV s}^{-1}$ . The dashed diagonal line corresponds to the extrapolation of the infinite sweep rate capacitance using the capacity between 2 and 20  $\text{mV s}^{-1}$ . **d**, The variation of the cathodic peak voltage with the sweep rate exhibits a region of small peak separation followed by increased separation at 20  $\text{mV s}^{-1}$ , and represents another method of identifying systems with facile intercalation kinetics.

relationship with the sweep rate leads to<sup>8</sup>:

$$i = a\nu^b$$

where  $a$  and  $b$  are adjustable values. Whereas a  $b$ -value of 0.5 would indicate that the current is controlled by semi-infinite linear diffusion, a value of 1 indicates that the current is surface-controlled. For sweep rates ranging from 0.1 to 20  $\text{mV s}^{-1}$ , corresponding to charging times  $>60$  s, the  $b$ -value for both the cathodic and anodic peaks is 1, indicating that the kinetics are surface-controlled, and thus fast. Figure 1b also exhibits a change in the slope of the anodic and cathodic peak currents at  $\sim 50$   $\text{mV s}^{-1}$ . This change in slope corresponds to a decrease in  $b$ -value to 0.8 and 0.7 for the cathodic and anodic currents, respectively, at sweep rates  $>50$   $\text{mV s}^{-1}$  (charging times  $<20$  s). This limitation to the rate capability can arise from numerous sources including an increase of the ohmic contribution (active material resistance, solid–electrolyte interphase resistance) and/or diffusion constraints/limitations<sup>11</sup>. In the limit of slow diffusion,  $b$  would approach a value of 0.5 as described above.

The relationship between capacity and sweep rate can also establish the rate-limiting step of a charge-storage mechanism<sup>12</sup>. In a plot of  $Q$  versus  $\nu^{-1/2}$ , regions that are linear represent capacity limited by semi-infinite linear diffusion whereas capacitive contributions are independent of the sweep rate. At sweep rates below 20  $\text{mV s}^{-1}$ , the extrapolated  $y$ -intercept yields the infinite sweep rate capacitance<sup>13</sup>. Figure 1c shows the plot of normalized capacity versus  $\nu^{-1/2}$  for  $T\text{-Nb}_2\text{O}_5$  from 1 to 500  $\text{mV s}^{-1}$  (the gravimetric capacity for the thin-film electrode is shown in Supplementary Fig. S2). Analogous to the behaviour of the peak current in Fig. 1b, there are two distinct regions in Fig. 1c. In region 1, at sweep rates  $<20$   $\text{mV s}^{-1}$ , the capacity is mostly independent of sweep rate. The magnitude of the capacity is  $\sim 130$   $\text{mAh g}^{-1}$  or  $\sim 65\%$  of the theoretical value based on a two-electron redox reaction with  $\text{Nb}_2\text{O}_5$ . In this range, solid-state lithium-ion diffusion is not the rate-limiting step for charge storage. In region 2, from 50 to 500  $\text{mV s}^{-1}$ , the capacity decreases linearly with  $\nu^{-1/2}$ . This indicates that charge storage is mainly diffusion-controlled at high sweep rates. That is, for charging times

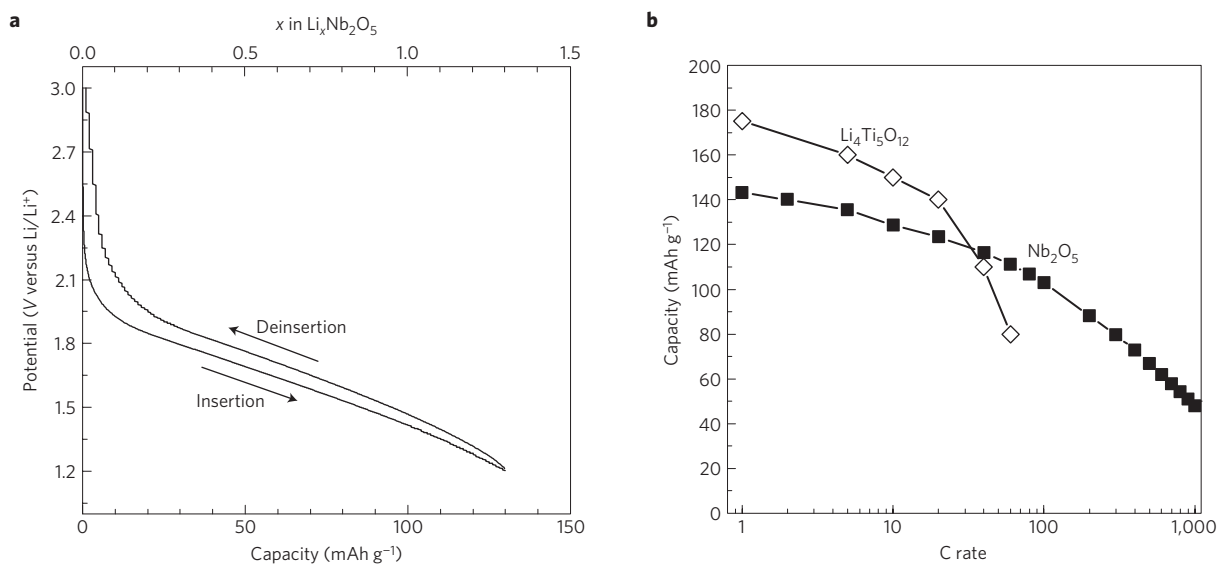

**Figure 2 | Electrochemical cycling of a 40- $\mu\text{m}$ -thick  $T\text{-Nb}_2\text{O}_5$  electrode. a,** Galvanostatic cycling of a thick  $\text{Nb}_2\text{O}_5$  electrode at a 10C rate. **b,** Comparison of the rate capability of  $T\text{-Nb}_2\text{O}_5$  with a high-rate lithium-ion anode,  $\text{Li}_4\text{Ti}_5\text{O}_{12}$ , at various C-rates ( $\text{Li}_4\text{Ti}_5\text{O}_{12}$  data reproduced from ref. 16).

of  $<20$  s, diffusion is rate-limiting, similar to most traditional battery electrodes. However, for charging times of 1 min (60C) or longer, there is no indication of diffusion limitations and this intercalation-based system behaves in a fully capacitive manner.


Another feature of  $T\text{-Nb}_2\text{O}_5$  at sweep rates  $<20$   $\text{mV s}^{-1}$  is that the peak voltage shifts with sweep rate are small (Fig. 1d). The cathodic peak shift is  $<0.1$  V at sweep rates below  $10$   $\text{mV s}^{-1}$ . As a result, the anodic and cathodic peaks overlap at  $0.1$   $\text{mV s}^{-1}$  (Supplementary Fig. S3) and it is in this behaviour that the similarity to surface redox reactions is most apparent<sup>14</sup>. In many lithium-ion intercalation materials, the peak separation is significant even in thin films and at slow sweep rates (for example,  $\Delta E_p = 0.13$  V for  $\text{LiCoO}_2$  at  $0.1$   $\text{mV s}^{-1}$ ; ref. 15). This type of behaviour is often associated with crystallographic phase changes during the Faradaic process, and contrasts with intercalation materials that form a solid solution, such as  $T\text{-Nb}_2\text{O}_5$ . Besides identifying facile intercalation, the peak voltage separation is related to the high-power capability of a material. As the charging time decreases, that is, at higher current densities, the peak separation in a battery material increases owing to polarization (reflecting the higher overpotentials necessary to deliver the higher currents), so that at higher rates the energy required to fully charge the material is significantly larger than the energy available on discharge.

The high-rate behaviour of  $T\text{-Nb}_2\text{O}_5$  is not limited to thin films or to experiments with small amounts of active material. The constant-current charge/discharge of a  $40\text{-}\mu\text{m}$ -thick  $T\text{-Nb}_2\text{O}_5$  ( $1$   $\text{mg cm}^{-2}$ ) electrode at a 10C rate is shown in Fig. 2a. At this rate, the capacity is  $130$   $\text{mAh g}^{-1}$  and  $E$  varies linearly with  $Q$  as expected for a pseudocapacitive process from equation (1). This represents capacities typical of battery materials but at rates closer to those of supercapacitors. The rate capability of  $T\text{-Nb}_2\text{O}_5$  from 1 to 1,000C is shown in Fig. 2b and compared with that of  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  (of comparable electrode dimensions)<sup>16</sup>.  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  is chosen as an example of a high-rate lithium-ion anode material. The rate capability for  $T\text{-Nb}_2\text{O}_5$  is significantly better than  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  above 30C and even at a 1,000C rate the capacity of the thick  $T\text{-Nb}_2\text{O}_5$  electrode is  $\sim 40$   $\text{mAh g}^{-1}$ . The thick electrode results verify that the intercalation pseudocapacitance mechanism is not due to thin-film or surface effects, such as vacancies or contributions of the first few atoms from the surface. Indeed, even for the thick electrode, the  $b$ -values for the anodic and cathodic peak currents are 1 from 1 to  $10$   $\text{mV s}^{-1}$  (Supplementary Fig. S4).

The high-rate capability of  $T\text{-Nb}_2\text{O}_5$  implies that the crystal structure permits exceptionally rapid ionic transport. As shown in Fig. 3a, the unit cell has sheets of edge- or corner-sharing distorted polyhedra lying parallel to the (001) plane, with each  $\text{Nb}^{5+}$  surrounded by either 6 or 7  $\text{O}^{2-}$ . The polyhedra are exclusively corner-sharing along the [001] direction with 5% of the  $\text{Nb}^{5+}$  ions randomly located in 9-coordinate sites between the (001) polyhedral planes<sup>17</sup>. The mostly empty octahedral sites between (001) planes provide natural tunnels for lithium-ion transport throughout the  $a$ - $b$  plane. Calculations indicate that the (001) plane allows degenerate pathways with low energy barriers for ion transport<sup>18</sup>.

A previous *in situ* X-ray diffraction study showed that the insertion of lithium into  $T\text{-Nb}_2\text{O}_5$  results in a solid solution with no apparent phase changes<sup>19</sup>, and negligible changes to lattice constants<sup>2</sup> and unit-cell volume<sup>20</sup> up to  $\sim 1.25$   $\text{Li}^+/\text{Nb}_2\text{O}_5$ . *In situ* X-ray absorption spectroscopy (XAS) demonstrated that lithiation reduces  $\text{Nb}^{5+}$  to  $\text{Nb}^{4+}$  (ref. 19). The *in situ* XAS studies carried out here confirm that lithiation results in a continuous change in oxidation state (Fig. 3b) and the Fourier-transform of the extended X-ray absorption fine structure (EXAFS) indicates that the insertion reaction proceeds through two stages (Fig. 3c). From 2.5 to 1.75 V, the EXAFS signal from the various Nb–O bond lengths in  $\text{Nb}_2\text{O}_5$  (1.40–1.85 Å) merges to a single peak at an intermediate bond length (1.75 Å), indicating that lithiation increases the Nb-centred symmetry. The lithiation is probably faster at low  $\text{Li}^+$  levels<sup>20</sup> owing to greater availability of sites and less interaction between cations. At lower potentials, the new EXAFS peak shifts to longer bond distances (1.85 Å) as a consequence of increased Li–O interactions at higher  $\text{Li}^+$  content. These structural studies emphasize the value of an open, layered structure to enable rapid ion transport within the active material.

The results presented in this study establish that  $T\text{-Nb}_2\text{O}_5$  exhibits electrochemical features of a pseudocapacitive material despite charge storage occurring in the bulk. Such behaviour is consistent with intercalation pseudocapacitance. The electrochemical features indicative of this mechanism are currents that are linearly proportional to the sweep rate, capacity that does not vary significantly with charging time, and peak potentials that do not shift significantly with sweep rate. A key design rule for intercalation pseudocapacitance at the atomic scale is a structure that does not undergo phase transformations on intercalation. In addition, facile two-dimensional (2D) lithium-ion diffusion pathways are

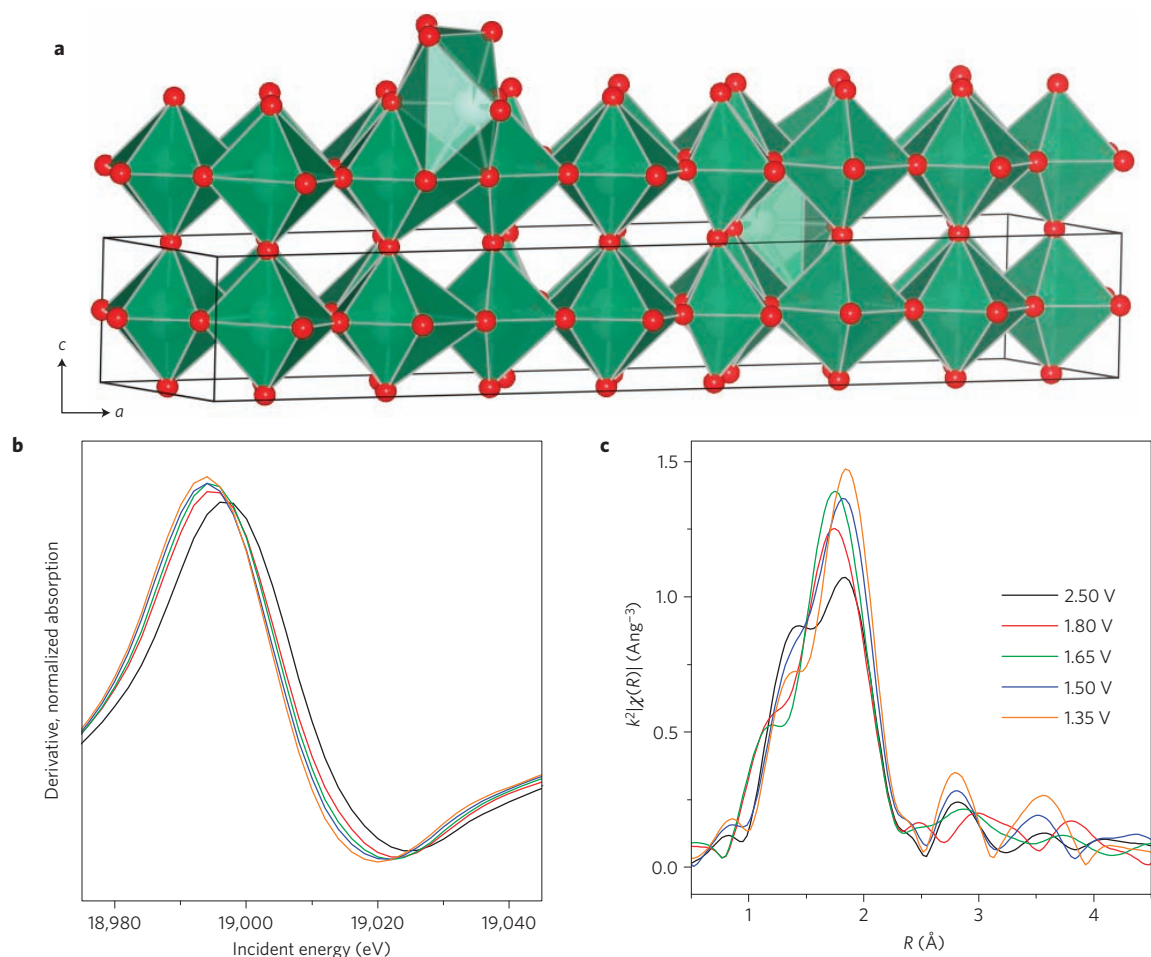

**Figure 3 | Structural features of lithium intercalation in  $T\text{-Nb}_2\text{O}_5$ .** **a**, The structure of  $T\text{-Nb}_2\text{O}_5$  stacked along the  $c$  axis demonstrates the layered arrangement of oxygen (red) and niobium (inside polyhedra) atoms along the  $a$ - $b$  plane. **b**, Derivative of Nb K-edge X-ray absorption near-edge spectra at selected cell voltages, showing a systematic shift to lower energies as  $\text{Nb}^{5+}$  is reduced to  $\text{Nb}^{4+}$ . **c**,  $k^2$ -weighted Fourier-transformed Nb K-edge EXAFS at selected cell voltages.

**Table 1 | Comparison between charge storage in two different pseudocapacitive materials.**

	$\text{RuO}_2 \cdot x\text{H}_2\text{O}$	$T\text{-Nb}_2\text{O}_5$
Electrolyte	$\text{H}^+$ , aqueous <sup>21</sup>	$\text{Li}^+$ , non-aqueous
Structure	Amorphous/nanocrystalline <sup>22,23</sup>	Crystalline
Structural water	Necessary for proton conduction <sup>22</sup>	Not necessary
Charge storage mechanism	Surface/near-surface <sup>23,24</sup>	Bulk
Pseudocapacitance type	Surface redox	Intercalation

$\text{RuO}_2 \cdot x\text{H}_2\text{O}$  and  $T\text{-Nb}_2\text{O}_5$  both exhibit capacitive behaviour. The mechanism of charge storage, however, is different and results in different structural requirements for high capacitance.

important. Charge storage that behaves as a quasi-2D process exhibits similar behaviour to 2D surface adsorption reactions<sup>14</sup>. These features contrast with those of pseudocapacitive  $\text{RuO}_2 \cdot x\text{H}_2\text{O}$  where charge storage occurs mainly on the surface or near-surface<sup>21-24</sup> as summarized in Table 1.

The results here are exciting because they demonstrate that for charging times as fast as 1 min (60C rate), there are no diffusion limitations in  $T\text{-Nb}_2\text{O}_5$ . As the high-rate capability is

due to fast ion diffusion in the bulk, this mechanism may be very good for thick electrodes because surface exposure to the electrolyte is not critical. To achieve devices with high energy density, further engineering at the nanoscale and beyond will be necessary to preserve the atomic-scale behaviour observed in thin films and microelectrodes. In particular, maintaining proper electronic conduction pathways will be critical.

## Methods

**Synthesis.** The synthesis of  $T\text{-Nb}_2\text{O}_5$  nanocrystals was reported previously<sup>2</sup>. Briefly, 2.56 mmol of  $\text{NbCl}_5$  (Sigma-Aldrich) was dissolved in 2 ml of ethanol (Fisher Scientific). In a separate vial, 0.23 ml of deionized water was mixed with 2 ml of ethanol. Both vials were then chilled for 2 h. The two solutions were then mixed together while 1 ml of propylene oxide (Sigma-Aldrich) was slowly added, forming a transparent gel. This gel was aged for 1 day and then soaked in acetone (Fisher Scientific) for 5 days. After supercritical drying with  $\text{CO}_2$ , the gel was transformed into an amorphous  $\text{Nb}_2\text{O}_5$  aerogel. Crystallization to the  $T$ -phase occurred by heat treatment at 600 °C for 2 h in air.

**Characterization.** Thin-film electrodes were fabricated by drop-casting a well-sonicated solution of  $T\text{-Nb}_2\text{O}_5$  in ethanol onto an oxygen plasma etched stainless-steel foil (Alfa Aesar). For thin-film measurements, lithium foils (Sigma-Aldrich) served as the reference and counter electrodes, and the electrolyte was 1 M  $\text{LiClO}_4$  (Sigma-Aldrich) in propylene carbonate (Sigma-Aldrich). The microelectrode preparation was described elsewhere<sup>9</sup>. Briefly,  $T\text{-Nb}_2\text{O}_5$  active material and carbon black (Timcal Super C65) powders were mixed in a 1:1 weight ratio to ensure good electrical contact. The mixture was packed into the microcavity (30  $\mu\text{m}$  depth, 30  $\mu\text{m}$  width), and subsequently immersed in the electrolyte. A 1  $\text{cm}^2$  platinum foil (Alfa Aesar) was used as the counter electrode

and lithium foil served as the reference. Thick Nb<sub>2</sub>O<sub>5</sub> electrodes were prepared by mixing the active material, carbon black (Timcal Super C65) and PVdF (Kynar) binder in a 80:10:10 weight ratio. The slurry was drop-cast onto 12-mm-diameter aluminium-disc current collectors and dried at 80 °C for 12 h. The electrode loading was between 1 and 1.5 mg cm<sup>-2</sup> with a thickness of 40 ± 5 μm. Measurements of the thick Nb<sub>2</sub>O<sub>5</sub> electrodes were performed in three-electrode Swagelok cells with the Nb<sub>2</sub>O<sub>5</sub> electrode as the working electrode, activated carbon as the counter electrode, a glass fibre separator (Whatman, GF/A) saturated with 1 M LiClO<sub>4</sub> in propylene carbonate, and a lithium foil reference. All measurements were carried out in argon-filled glove boxes between 1.2 and 3 V (versus Li/Li<sup>+</sup>) with oxygen and moisture levels of <1 ppm and using PAR EG&G 273 and Bio-Logic VMP3 potentiostats.

*In situ* X-ray absorption was performed using thin films of T-Nb<sub>2</sub>O<sub>5</sub> cast from a well-sonicated ethanol solution onto carbon-coated aluminium. 2032-type coin cells were modified to include an X-ray window by drilling ~3-mm-diameter holes through the cathode casing and epoxying a 125-μm-thick Kapton window on the outside of the casing. Both sides of the window were then coated with 100-nm-thick aluminium layers using a vacuum evaporator. Cells were assembled with a lithium anode, a 1 M LiClO<sub>4</sub> in propylene carbonate electrolyte, and a Whatman glassy fibre separator.

## References

- Brezesinski, K. *et al.* Pseudocapacitive contributions to charge storage in highly ordered mesoporous Group V transition metal oxides with iso-oriented layered nanocrystalline domains. *J. Am. Chem. Soc.* **132**, 6982–6990 (2010).
- Kim, J. W., Augustyn, V. & Dunn, B. The effect of crystallinity on the rapid pseudocapacitive response of Nb<sub>2</sub>O<sub>5</sub>. *Adv. Energy Mater.* **2**, 141–148 (2012).
- Conway, B. E. *Electrochemical Supercapacitors: Scientific Fundamentals and Technological Applications* (Kluwer-Academic, 1999).
- Herrero, E., Buller, L. J. & Abruña, H. D. Underpotential deposition at single crystal surfaces of Au, Pt, Ag and other materials. *Chem. Rev.* **101**, 1897–1930 (2001).
- Huggins, R. A. Supercapacitors and electrochemical pulse sources. *Solid State Ion.* **134**, 179–195 (2000).
- Angerstein-Kozłowska, H., Klinger, J. & Conway, B. E. Computer simulations of the kinetic behavior of surface reactions driven by a linear potential sweep. Part I: Model 1-electron reaction with a single adsorbed species. *J. Electroanal. Chem.* **75**, 45–60 (1977).
- Brezesinski, T., Wang, J., Polleux, J., Dunn, B. & Tolbert, S. H. Templated nanocrystal-based porous TiO<sub>2</sub> films for next-generation electrochemical capacitors. *J. Am. Chem. Soc.* **131**, 1802–1809 (2009).
- Lindström, H. *et al.* Li<sup>+</sup> insertion in TiO<sub>2</sub> (anatase). 2. Voltammetry on nanoporous films. *J. Phys. Chem. B* **101**, 7717–7722 (1997).
- Come, J., Taberna, P.-L., Hamelet, S., Masquelier, C. & Simon, P. Electrochemical kinetic study of LiFePO<sub>4</sub> using cavity microelectrode. *J. Electrochem. Soc.* **158**, A1090–A1093 (2011).
- Ohzuku, T., Sawai, K. & Hirai, T. Electrochemistry of L-niobium pentoxide in a lithium/non-aqueous cell. *J. Power Sources* **19**, 287–299 (1987).
- Park, M., Zhang, X., Chung, M., Less, G. B. & Sastry, A. M. A review of conduction phenomena in Li-ion batteries. *J. Power Sources* **195**, 7904–7929 (2010).
- Ardizzone, S., Fregonara, G. & Trasatti, S. ‘Inner’ and ‘outer’ active surface of RuO<sub>2</sub> electrodes. *Electrochim. Acta* **35**, 263–267 (1990).
- Baronetto, D., Krstajić, N. & Trasatti, S. Reply to Note on a method to interrelate inner and outer electrode areas by H. Vogt. *Electrochim. Acta* **39**, 2359–2362 (1994).
- Conway, B. E. Transition from ‘supercapacitor’ to ‘battery’ behavior in electrochemical energy storage. *J. Electrochem. Soc.* **138**, 1539–1548 (1991).
- Xia, H., Lu, L. & Ceder, G. Substrate effect on the microstructure and electrochemical properties of LiCoO<sub>2</sub> thin films grown by PLD. *J. Alloys Compd.* **417**, 304–310 (2006).
- Zhang, N. Q. *et al.* Facile preparation of nanocrystalline Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub> and its high electrochemical performance as anode material for lithium-ion batteries. *Electrochem. Commun.* **13**, 654–656 (2011).
- Kato, K. & Tamura, S. The crystal structure of T-Nb<sub>2</sub>O<sub>5</sub>. *Acta Cryst.* **B31**, 673–677 (1975).
- Liu, C.-P., Zhou, F. & Ozolins, V. First principles study for lithium intercalation and diffusion behavior in orthorhombic Nb<sub>2</sub>O<sub>5</sub> electrochemical supercapacitor. *American Physical Society March Meeting 2012* abstr. B26.00003. Accessed March 20, 2013. <http://meetings.aps.org/link/BAPS.2012.MAR.B26.3>.
- Kodama, R., Terada, Y., Nakai, I., Komaba, S. & Kumagai, N. Electrochemical and *in situ* XAFS-XRD investigation of Nb<sub>2</sub>O<sub>5</sub> for rechargeable lithium batteries. *J. Electrochem. Soc.* **153**, A583–A588 (2006).
- Kumagai, N., Koishikawa, Y., Komada, S. & Koshiba, N. Thermodynamics and kinetics of lithium intercalation into Nb<sub>2</sub>O<sub>5</sub> electrodes for a 2 V rechargeable lithium battery. *J. Electrochem. Soc.* **146**, 3203–3210 (1999).
- Long, J. W., Swider, K. E., Merzbacher, C. I. & Rolison, D. R. Voltammetric characterization of ruthenium oxide-based aerogels and other RuO<sub>2</sub> solids: The nature of capacitance in nanostructured materials. *Langmuir* **15**, 780–785 (1999).
- Zheng, J. P., Cygan, P. J. & Jow, T. R. Hydrated ruthenium oxide as an electrode material for electrochemical capacitors. *J. Electrochem. Soc.* **142**, 2699–2703 (1995).
- Dmowski, W., Egami, T., Swider-Lyons, K. E., Love, C. T. & Rolison, D. R. Local atomic structure and conduction mechanism of nanocrystalline hydrous RuO<sub>2</sub> from X-ray scattering. *J. Phys. Chem. B* **106**, 12677–12683 (2002).
- Liu, Y., Zhou, F. & Ozolins, V. *Ab initio* study of the charge-storage mechanisms in RuO<sub>2</sub>-based electrochemical ultracapacitors. *J. Phys. Chem. C* **116**, 1450–1457 (2012).

## Acknowledgements

This work was supported by the Molecularly Engineered Energy Materials and the Energy Materials Center at Cornell, Energy Frontiers Research Centers funded by the US DOE Office of Basic Energy Sciences (DE-SC001342 and DE-SC0001086, respectively). XAS was performed at the Cornell High Energy Synchrotron Source, supported by the NSF and NIH/NIGMS (DMR-0936384). M.A.L. acknowledges support from the US DOD National Defense Science and Engineering Fellowship. J.C. was supported by Delegation Generale pour l’Armement (DGA). P.S. and P.-L.T. acknowledge the support from the European Research Council (ERC, Advanced Grant, ERC-2011-AdG, Project 291543—IONACES) and the Chair of Excellence ‘Embedded multi-functional nanomaterials’ from the EADS Foundation.

## Author contributions

V.A., J.C., M.A.L. and J.W.K.: experimental work, data analysis. P.-L.T., S.H.T., H.D.A., P.S., B.D.: project planning, data analysis.