



HAL
open science

Local response to light excitation in the charge-ordered phase of (EDO-TTF) 2 SbF 6

M. Servol, Nicolas Moisan, Eric Collet, Hervé Cailleau, Wawrzyniec Kaszub, Loic Toupet, Davide Boschetto, Tadahiko Ishikawa, Alain Moréac, Shin-Ya Koshihara, et al.

► **To cite this version:**

M. Servol, Nicolas Moisan, Eric Collet, Hervé Cailleau, Wawrzyniec Kaszub, et al.. Local response to light excitation in the charge-ordered phase of (EDO-TTF) 2 SbF 6. *Physical Review B: Condensed Matter and Materials Physics (1998-2015)*, 2015, 92 (2), pp.024304. 10.1103/PhysRevB.92.024304 . hal-01168113v1

HAL Id: hal-01168113

<https://hal.science/hal-01168113v1>

Submitted on 25 Jun 2015 (v1), last revised 5 May 2017 (v2)

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Local response to light excitation in the charge-ordered phase of (EDO-TTF)₂SbF₆

Marina Servol^{1,*}, Nicolas Moisan¹, Eric Collet¹, Hervé Cailleau¹, Wawrzyniec Kaszub¹,
Loïc Toupet¹, Davide Boschetto², Tadahiko Ishikawa³, Alain Moréac¹, Shin-ya
Koshihara³, Mitsuhiro Maesato⁴, Mikio Uruichi⁵, Xiangfeng Shao⁶, Yoshiaki Nakano⁶,
Hideki Yamochi⁶, Gunzi Saito^{4,6}, Maciej Lorenc¹

¹Institut de Physique de Rennes, UMR 6251 CNRS-University Rennes 1 campus Beaulieu,
Rennes, 35042, France

²Laboratoire d'Optique Appliquée, Ecole Nationale Supérieure des Techniques Avancées,
Palaiseau, France

³ Department of Materials Science, Tokyo Inst. of Technology, 2-12-1, Oh-okayama, Meguro,
Tokyo, 152-8551, Japan,

⁴ Division of Chemistry, Graduate School of Science, Kyoto University, Sakyo-ku, Kyoto,
606-8501, Japan

⁵ Institute for Molecular Science, Myodaiji, Okazaki 444-8585, Japan

⁶ Research Center for Low Temperature and Materials Sciences, Kyoto University, Sakyo-ku,
Kyoto, 606-8502, Japan

ABSTRACT

The family of materials (EDO-TTF)₂XF₆ represents quasi-one-dimensional ¼ filled systems exhibiting insulator-to-metal (I-M) phase transition at thermal equilibrium. (EDO-TTF)₂PF₆ is known to undergo a photoinduced I-M conversion with cooperative response to light excitation. Here we use femtosecond pump-probe experiments to study the photoresponse of (EDO-TTF)₂SbF₆ made of a larger counter-anion SbF₆ compared to the well studied (EDO-TTF)₂PF₆. In the early stage of the photoinduced process, we reveal a multi-component coherent oscillating feature. The evolution of this feature with excitation density and temperature points to the local nature of the photoswitching in (EDO-TTF)₂SbF₆. At longer timescale, we did not detect the features associated with the transformation to the M phase, albeit observed in the PF₆ derivative. We propose a scenario whereby the bigger size of the counter-anion in (EDO-TTF)₂SbF₆ hinders the establishment of this transformation at macroscopic scale.

I. INTRODUCTION

The development of ultrafast time-resolved spectroscopies, and especially the pump-probe techniques, gives new possibilities for tracking and controlling dynamical transformations in the solid state on ultrashort time scale. An intense pump laser pulse prepares the system in a highly excited state involving a bunch of excited electrons, and a probe pulse monitors their temporal evolution thereby providing information on the triggered collective and/or cooperative phenomena. This technique makes it possible to track coherent atomic/molecular motions and physical transformations of a material in real time. During the last decade, the field of ultrafast photoinduced transformation has been expanding rapidly along diverse directions: correlated electrons, charge density waves, magnetism, molecular switching, etc¹⁻⁴. A typical example is provided by a quasi-one-dimensional quarter filled organic conductor $(\text{EDO-TTF})_2\text{PF}_6$ where EDO-TTF is the abbreviation of the electron donor (D) molecule ethylenedioxytetrathiafulvalene. It exhibits first-order insulator-to-metal (I-M) phase transition at thermal equilibrium and a gigantic ultrafast change of reflectivity under irradiation by a laser pulse in the I phase⁵. It was shown by time-resolved optical^{6, 7} and vibrational spectroscopy⁸ as well as ultrafast electron diffraction⁹ that the photoinduced transformation proceeds stepwise. The initial electronic excited state is trapped at the molecular level within 40 fs following the electron-phonon coupled precursor state⁷ while the crystal transformation is driven by slower propagation at the 100 ps timescale. Actually, different isostructural compounds of the same $(\text{EDO-TTF})_2\text{XF}_6$ family, where X stands for P, As or Sb, have already been synthesized. They undergo similar I-M phase transition at thermal equilibrium. However, the transition temperature is decreased and the width of thermal hysteresis is increased with increasing anion size¹⁰.

The phase transition at thermal equilibrium of $(\text{EDO-TTF})_2\text{PF}_6$ between M and I phases reveals different facets such as Peierls distortion and charge ordering, as well as a significant reduction of the orientational disorder of XF_6 counter anions. The main feature is the charge order along donor stack $(\text{D}^0\text{D}^1\text{D}^1\text{D}^0)$, in contrast to the more common order $(\text{D}^1\text{D}^0\text{D}^1\text{D}^0)$ ¹¹⁻¹³. For photoinduced transformation, the similarity between relaxation dynamics of reflectivity and optical conductivity, both occurring on the microsecond scale, indicates that a transient metallic state is generated on this timescale⁵. Additional experimental measurements⁶ showed that the reflectivity spectrum of the photoinduced state

differs on the ultrashort timescale from that of the metallic state at thermal equilibrium, when seen over a broad energy range from 69 meV to 2.1 eV. These results, combined with theoretical investigations, demonstrated that a photoexcitation of the charge-ordered insulator ($D^0D^1D^1D^0$) into its charge-transfer band around 1.58 eV does not create directly a metallic phase through charge melting ($D^{0.5}D^{0.5}D^{0.5}D^{0.5}$) but rather leads to a photoinduced ($D^1D^0D^1D^0$) state at the picosecond timescale. Recently, time resolved vibrational spectroscopy⁸ and ultrafast electron diffraction measurements⁹ unveiled that the photoinduced phase similar to the metallic one of the high temperature phase is only reached around 100 ps. During the relaxation from the photoexcited electronic state to the photoinduced ($D^1D^0D^1D^0$) state, a coherent phonon with frequency around 2 THz was also observed⁵. In parallel to these experimental studies¹⁵, theoretical attempts have been undertaken to explain the unusual ($D^0D^1D^1D^0$) order of the insulating phase and the photoinduced phase transition^{6,13-16}.

The question whether the anion size favours either local or 3D photoinduced transformation has hitherto not been addressed. In this paper, we investigate the response to femtosecond laser excitation of the (EDO-TTF)₂SbF₆ derivative, which is isostructural to (EDO-TTF)₂PF₆ but for a larger anion size. In particular, the coherent dynamics at the picosecond timescale is studied, revealing the generation of several coherent phonons. In section II, the experimental procedure and especially the femtosecond pump-probe experiment is presented. In section III, we describe the insulating to metal phase transition occurring at thermal equilibrium in the SbF₆ derivative by using structural and electronic probes for tracking the degrees of freedom involved. In parallel, we highlight the differences with the case of (EDO-TTF)₂PF₆. In section IV, the ultrafast dynamics is presented and in section V, we provide a comprehensive analysis of the optical data obtained together with a phenomenological description of the anion size effect.

II EXPERIMENTAL DETAILS

Different complementary experiments were used for characterizing the I-M phase transition of (EDO-TTF)₂SbF₆ at thermal equilibrium. X-ray diffraction was performed on single crystals with typical sizes of $600 \times 200 \times 100 \mu\text{m}^3$. The diffraction experiments were carried out on a Xcalibur 3 four-circles diffractometer (Oxford Diffraction) equipped with a 2D sapphire 3 CCD detector with Mo K α radiation ($\lambda=0.71069 \text{ \AA}$). The single crystals were

placed in Oxford Cryosystem nitrogen-flow cryostat with a temperature stability of 0.1 K. Crystals were initially flash-cooled to 100 K to avoid sample damage in the vicinity of the first-order phase transition and then heated to set temperature. Although the flash-cooling procedure could create phase domains, none was observed. The unit cell parameters and the data reduction were obtained with CrysAlis software from Oxford Diffraction¹⁸. The structures [Fig. 1] were solved with SIR-97¹⁹ and refined with SHELXL97²⁰. Magnetic susceptibility of the polycrystalline sample was measured with a Quantum Design MPMS-XL system and corrected for both the magnetization of the sample holder and the diamagnetic contribution of the sample itself. The estimation of the diamagnetic contribution was done using Pascal's constants. Raman spectra measurements were performed with an XY DILOR triple monochromator. Optical reflectivity data were obtained with tungsten-halogen lamp coupled to a monochromator (Spectral Products) for the light source, and a photodiode with a lock-in amplifier (Signal recovery) for detection.

In order to investigate the dynamics of the photoinduced response of (EDO-TTF)₂SbF₆, optical pump-probe experiments were performed. The laser system used consisted of a Ti:sapphire oscillator (MIRA, Coherent) delivering a 76 MHz train of 40 fs pulses centred at 1.55 eV. This train is amplified at 1 kHz by regenerative amplifier (LEGEND, Coherent) to 2.2 mJ. The beam is split into two, the pump and the probe beam, each pumping an optical parametric amplifier (TOPAS, Light Conversion)²¹. The wavelength of the two beams can be tuned from 0.41 eV to 6.2 eV. The pulse duration after the TOPAS is estimated to be 50 fs. The pump energy was set from 4 to 1400 $\mu\text{J}\cdot\text{cm}^{-2}$ (1 photon per 18000 to 55 molecules⁵) due to the sample damage above 1500 $\mu\text{J}\cdot\text{cm}^{-2}$. The probe fluency used was set to 1 $\mu\text{J}\cdot\text{cm}^{-2}$, so that it did not affect the sample response.

The pump-probe delay was set by a linear stage (IMS, Newport). In order to increase the temporal resolution, a collinear geometry between pump and pulse was chosen: the recombination of the two beams was done with a wedged half mirror. The cross-correlation between pump and probe gave final temporal resolution with full width at half maximum (FWHM) of around 80 fs.

The pump and the probe were focused on the crystal by lenses of 500 mm and 200 mm focal length, respectively, which resulted in beam-waists of 380 μm and 150 μm at FWHM. A larger spot was chosen for the pump, so that any small displacement of the pump beam would be negligible for the excitation of the probed part of the crystal. The polarization of both, pump and probe, were parallel to the EDO-TTF stacking axis of the crystal. An Oxford

Cryosystems nitrogen-flow cryostat was used to control the temperature, and the same flash-cooling procedure was applied as described above.

Finally, we detected the relative change in reflectivity with a phase sensitive lock-in detection (Stanford research). To perform this detection, the pumping rate of the crystal was halved to 500 Hz by an optical chopper. The 1 kHz probe impinged on the crystal excited at 500 Hz and the photodiode measured a reflectivity signal modulated at this latter frequency. The role of the lock-in amplifier was to recover the 500 Hz modulation signal. In order to take shot-to-shot fluctuations of the laser into account, the reflectivity signal was balanced with a reference signal sampled before the sample. At best, this detection method allowed sensitivity as high as 10^{-5} .

III I-M PHASE TRANSITION AT THERMAL EQUILIBRIUM

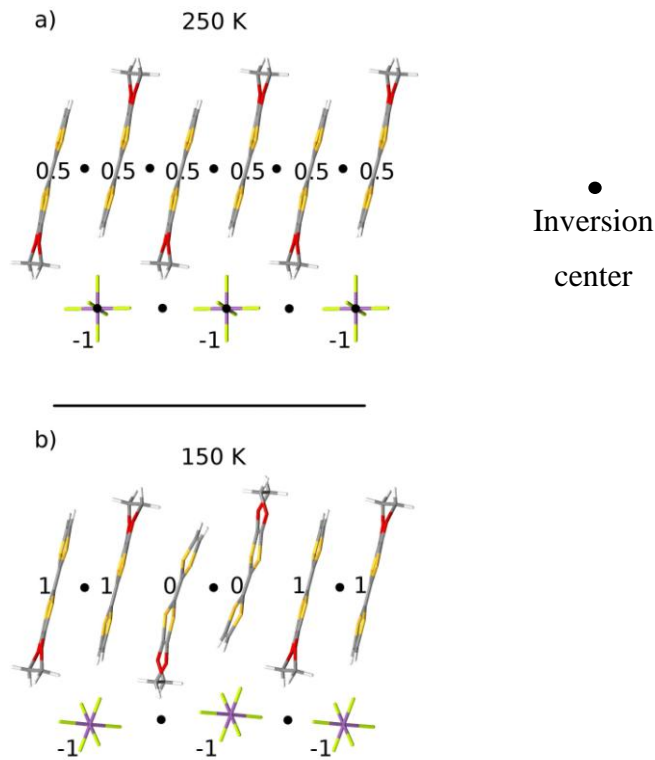


FIG. 1. (Color online) Crystal structures of the M (a) and I phase (b) and the corresponding schematic charge distribution on the D molecules. In the I phase, the symmetry breaking resulting from charge ordering involves important structural reorganization with, for example, the bending of the neutral molecules. Due to the cell doubling along the stack, the inversion symmetry is lowered, and the charge ordering accompanied by important modifications of the orientation of the SbF_6^- anions is observed.

The I-M transition in $(\text{EDO-TTF})_2\text{SbF}_6$ ²² at thermal equilibrium is similar to that observed for $(\text{EDO-TTF})_2\text{PF}_6$. In the high temperature M phase [Fig. 1], the space group is $P_{\bar{1}}$ and in the dimers formed by two head-to-tail D molecules, both D are equivalent by inversion symmetry located in-between them. As a result, the electron kept by one counter-anion corresponds to one hole distributed over two D, with formal charges +0.5 equal by symmetry. In the insulating phase, a symmetry breaking takes place with a cell doubling and the loss of half of the inversion centres. This generates two independent pairs of donor dimers centred on inversion symmetry with two different formal charges. These charges are empirically estimated from intermolecular bondlength obtained by X-ray diffraction^{11,23,24} or by maximum entropy method¹². The alternation of bent neutral and flat ionized dimers is characteristic of this charge order as observed at 150 K in Fig. 1. In other words, the symmetry breaking is associated with charge ordering process along the D stack. It can be schematically represented by $(\text{D}^{0.5}\text{D}^{0.5}\text{D}^{0.5}\text{D}^{0.5})$ in the M phase, and by $(\text{D}^0\text{D}^1\text{D}^1\text{D}^0)$ in the I phase.

However, some structural differences appear in the intermolecular organisation between the PF_6 and SbF_6 derivatives⁶. The main feature is that the larger size of the SbF_6^- anions results in a bigger unit cell. The distance b between D molecules is slightly longer for the SbF_6 derivative and, in addition, the interchain distance a is significantly larger. Consequently, the interchain coupling is weaker. The chemical substitution by larger anions compared to the case of the PF_6 derivative can be assimilated to a negative pressure effect and underlines the role of elastic interaction and volume change in the vicinity of phase transition. As a consequence, the transition toward the metallic phase occurs at a lower temperature ($T_{\text{I-M}}=242$ K) and shows a larger thermal hysteresis (22 K) for $(\text{EDO-TTF})_2\text{SbF}_6$ compared to $(\text{EDO-TTF})_2\text{PF}_6$ ($T_{\text{I-M}}=278$ K, 2.5 K width hysteresis)^{10,25}. It can be noted that for all derivatives of the isostructural $(\text{EDO-TTF})_2\text{XF}_6$ family, the phase transition occurs for almost the same critical value of the D chain cell parameter b and the magnitude of their discontinuous changes at $T_{\text{I-M}}$ is nearly the same¹⁰. This is very likely due to the strongly 1D character of the compound. Since this lattice parameter is larger for the SbF_6 derivative, the critical value of b is reached by thermal contraction at lower temperature than for $(\text{EDO-TTF})_2\text{PF}_6$. Unlike the intrachain cell parameter, the interchain cell parameters change significantly more as the anion size increases. The anions change their orientation at the phase transition and, it requires larger volume change to accommodate movements of bigger anions. Thus, the relative volume jump $\Delta V/V_{\text{HT}}$, where V_{HT} is the cell volume at high temperature, is

three times higher¹⁰ in the case of $(\text{EDO-TTF})_2\text{SbF}_6$ than in the case of $(\text{EDO-TTF})_2\text{PF}_6$. In other words, the first-order character of the phase transition is much stronger for the SbF_6 derivative than for the PF_6 one. The effect of coupling between the order parameter and the cell deformation is indeed stronger and costs more elastic energy. This is in agreement with the larger thermal hysteresis for $(\text{EDO-TTF})_2\text{SbF}_6$. The bigger size of anion makes the phase transition more difficult.

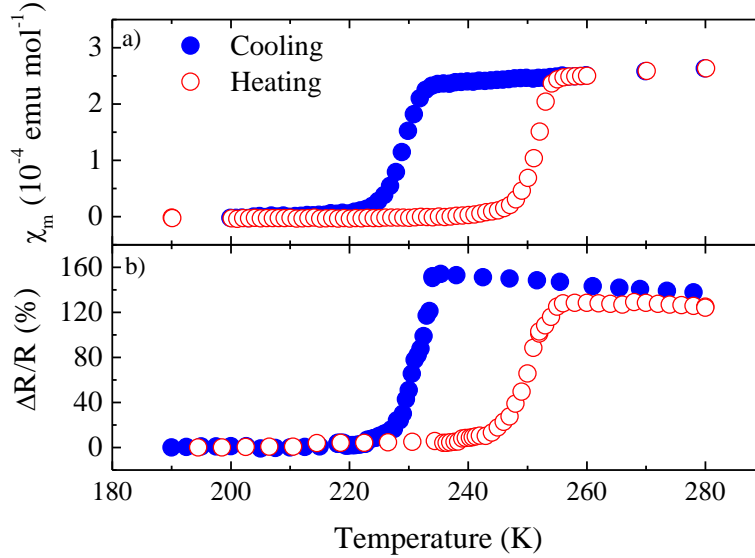


FIG. 2. (Color online) (a) Magnetic susceptibility of $(\text{EDO-TTF})_2\text{SbF}_6$ and (b) relative variation of the reflectivity at 1.72 eV as a function of temperature with a polarisation parallel to the D chain cell parameter b of $(\text{EDO-TTF})_2\text{SbF}_6$: the hysteresis is centred at 240 K and 22 K wide.

The I-M transition and its hysteresis are well observed by magnetic susceptibility χ_m as it vanishes in the I phase by electron pairing [Fig. 2(a)]. It entails an important change of electronic state which leads to significant changes of physical properties and especially of optical reflectivity. The reflectivity spectrum measured with light polarized along the D stacking axis of the crystal in both phases is shown in Fig. 3(a) and indicates that optical reflectivity variations can be used for probing the change of electronic state of this crystal. The relative variation of reflectivity at 1.72 eV with temperature exhibits a clear optical signature of the transition with a hysteretic behaviour in perfect agreement with magnetic data [Fig. 2(b)]. By applying Kramers-Krönig transformation to this reflectivity spectrum, we obtained optical conductivity of the sample [Fig. 3(b)]. The charge transfer (CT) band

corresponding to the CT excitation from $(D^0D^1D^1D^0)$ to localized $\{D^0D^2D^0D^0\}$, and referred to as CT2 for $(\text{EDO-TTF})_2\text{PF}_6$ ²⁴, is observed in the I phase around 1.29 eV²⁵.

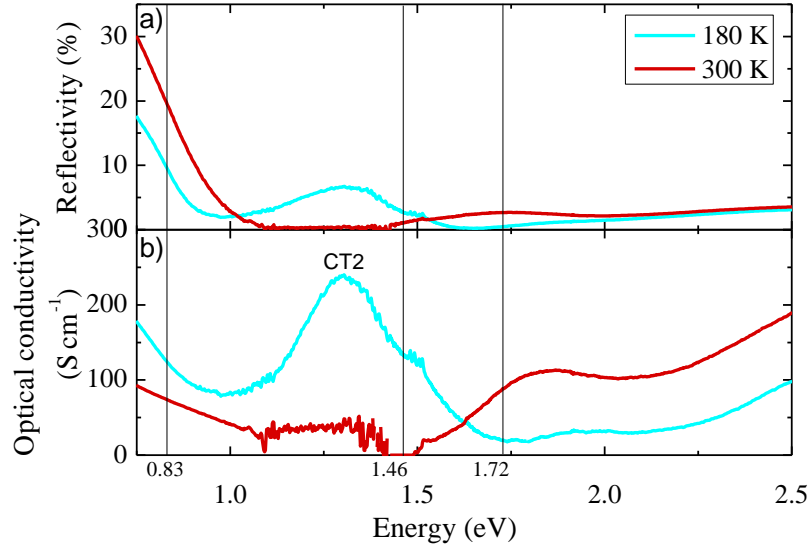


FIG. 3. (Color online) (a) Reflectivity R at different temperatures with a polarisation parallel to the D stacking axis of $(\text{EDO-TTF})_2\text{SbF}_6$. (b) Optical conductivity of $(\text{EDO-TTF})_2\text{SbF}_6$.

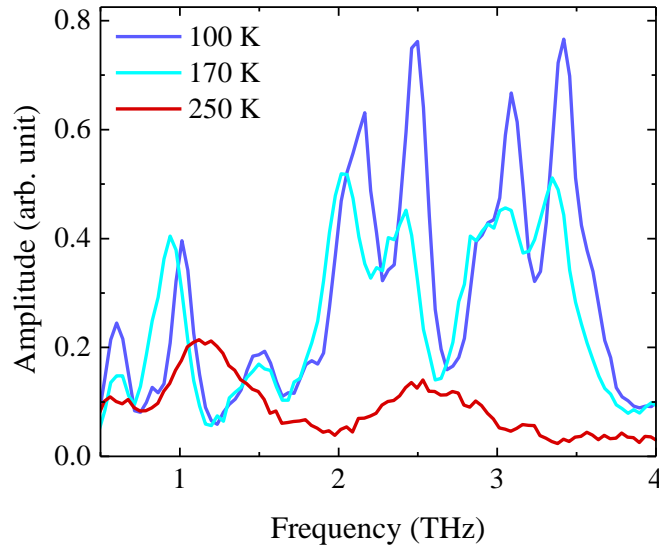


FIG. 4. (Color online) Raman spectra of $(\text{EDO-TTF})_2\text{SbF}_6$ in the I phase at 100 K and 170 K and in the M phase at 250 K.

Important changes of Raman spectra are also observed during the phase transition, resulting from the symmetry breaking (splitting of the band) and of the electronic redistribution (changes of frequencies) [Fig. 4]. In the M phase at 250 K, two intense and

broad peaks are clearly observed around 1.15 and 2.6 THz. In the low temperature I phase, at 100 K and 170 K, several modes are easily identified at around 1, 1.5, 2, 2.5, 2.9, 3.2 and 3.4 THz. The increase of the number of Raman active modes comes from the cell doubling, resulting in a doubling of phonon branches, whereas slight softening is observed between 100 and 170 K in the I phase for most of the modes. In molecular solids, such low frequency modes are attributed to intermolecular vibrations or librations mode, as well as intramolecular modes of boating-like nature^{23,26-30}.

IV PHOTOINDUCED DYNAMICS

To gain some insight into the photoinduced dynamics in the family of charge-transfer materials, we investigate here the response to femtosecond laser excitation of (EDO-TTF)₂SbF₆ in the I phase by using optical pump-probe spectroscopy. The pump energy was 1.46 eV, which is nearly resonant with the CT2 band. This scheme of excitation is similar to that used for (EDO-TTF)₂PF₆, and it efficiently drives photoinduced transformation. Two probe energies were used: 1.72 eV on the high energy side of the CT2 band, a region with a relatively good reflectivity in the high temperature phase, and 0.83 eV on the high energy side of the CT1 band²⁵ [Fig. 3].

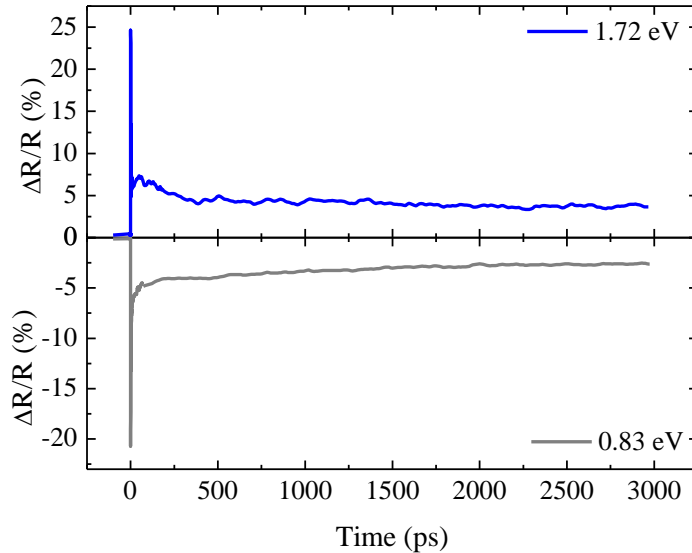


FIG. 5. (Color online) Photoresponse of (EDO-TTF)₂SbF₆ at 100 K for a 1.46 eV pump and 1.72 eV probe (upper graph) and 0.83 eV probe (lower graph).

In order to understand the first steps of the transformation in $(\text{EDO-TTF})_2\text{SbF}_6$, the experiments were conducted on the picosecond and nanosecond timescale at different temperatures. Figure 5 shows the typical time traces of the relative reflectivity variation $\Delta R/R$ at pump fluency of $600 \mu\text{J}\cdot\text{cm}^{-2}$. It shows an instantaneous peak reflecting the initial electronic photogenerated state $\{\text{D}^0\text{D}^2\text{D}^0\text{D}^0\}$ which decays exponentially in 300 fs [Fig. 6] to a long lived transient state. This state is different from the insulating ground state and persists over at least 3 ns. For the 1.72 eV probe energy, $\Delta R/R$ is positive [Fig 5(a)], as observed between I and M phase at thermal equilibrium. However, $\Delta R/R$ is negative at 0.83 eV [Fig 5(b)], whereas it is positive at thermal equilibrium going from I to M phase [Fig 3(a)]. This is a clear indication that this photoinduced state is different from both the insulating and the high temperature metallic states. This is in agreement with recent femtosecond electron diffraction⁹ and IR⁸ studies of $(\text{EDO-TTF})_2\text{PF}_6$, which revealed the formation of an intermediate state prior to M phase. This $(\text{D}^0\text{D}^1\text{D}^0\text{D}^1)$ state is characterized also by negative change in the 0.8 eV region of the reflectivity spectrum⁸. Our optical data therefore reveal the photo-generation of the $(\text{D}^0\text{D}^1\text{D}^0\text{D}^1)$ state in $(\text{EDO-TTF})_2\text{SbF}_6$.

A. Coherent phonons

The zoom on the time traces of $\Delta R/R$ data in the first 8 ps is shown in Figures 6(a-d), for which pump fluency was set to $1100 \mu\text{J}\cdot\text{cm}^{-2}$. The initial peak which decreases with a 300 fs time constant to the metastable state appears now clearly. A multi-component oscillation superimposed on the main signal can be observed and unveils some characteristics of the new state. These oscillations result from the simultaneous excitation of several optical coherent phonons as observed in other charge-transfer materials^{30, 31} and also in spin-crossover crystals³². We retrieved the oscillating part of the $\Delta R/R$ signal by subtracting the exponential decay of the electronic peak excitation convoluted with the temporal Gaussian for the laser pulse [Figs. 6(e-h)]. By extending the oscillating signal with zero padding on time domain, we performed Hanning windowed Fourier transform with a satisfactory frequency definition [Figs. 6(i-l)]. At 1.72 eV, three main modes appear at the different temperatures around 1, 2 and 2.5 THz, as well as weaker ones around 1.5, 2.9, 3.2 and 3.5 THz. At 0.83 eV, the same main modes are also observed at 1, 2 and 2.5 THz. This corroborates the results obtained at 1.72 eV.

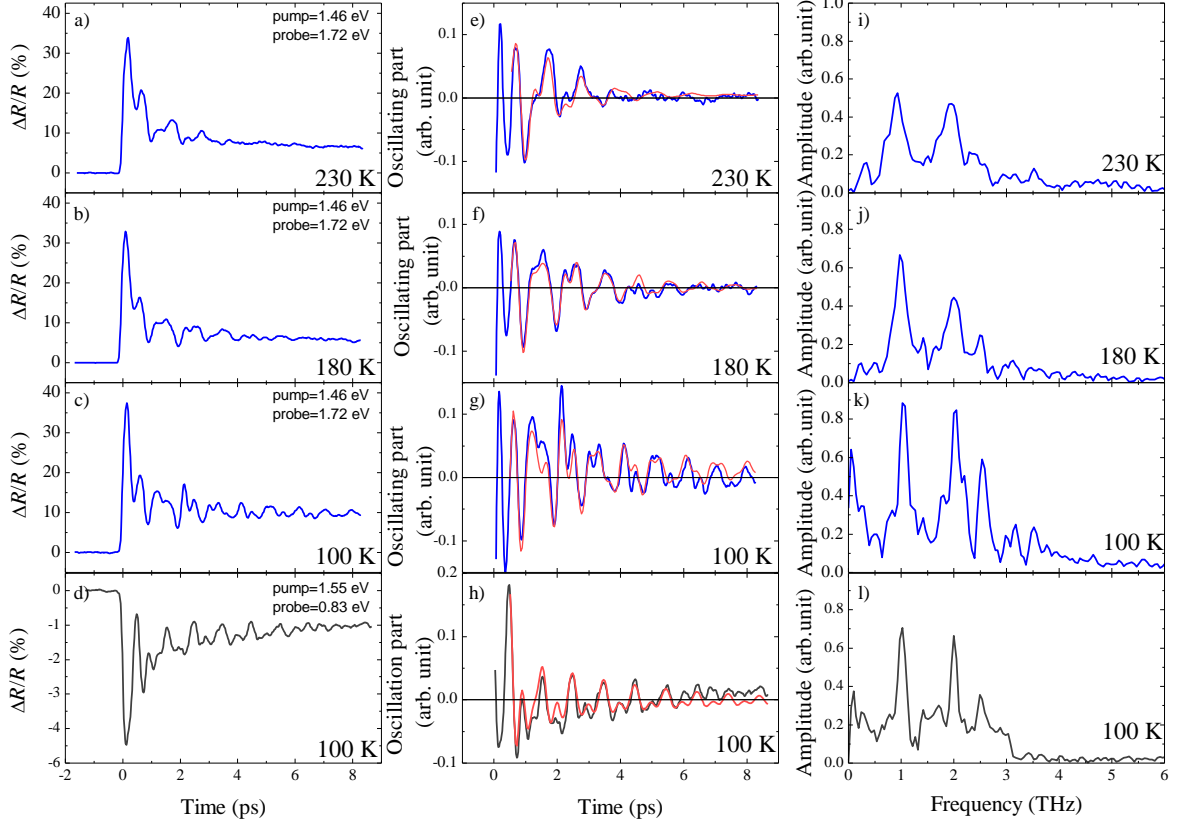


FIG. 6. (Color online) Photoresponse of $(\text{EDO-TTF})_2\text{SbF}_6$ at 100 K, 180 K and 230 K for a 1.46 eV pump and 1.72 eV probe (a-c) and a 1.55 eV pump and 0.83 eV probe (d). Oscillation part retrieved from the photoresponse and the corresponding fit (thin red – or light gray- lines) with 3 phonon modes (e-h correspond to a-d, respectively). The transformed Fourier spectra obtained from the oscillation (i-l correspond to e-h, respectively).

It can be noted that the global shape of the oscillations looks different depending on the probe energy used: while the mode at 2.9 THz is barely distinguishable, those at 3.2 and 3.5 THz are invisible at 0.83 eV [Figs. 6(l)]. Such ultrafast oscillation of optical reflectivity is generated by the activation of coherent optical phonons, which modulate the dielectric susceptibility through electron-phonon coupling. The contribution of a specific phonon to optical modulation is photon energy dependent³³ and explains the apparent relative change of the spectral weight of the modes for measurements using 0.83 and 1.72 eV probes.

In order to describe more accurately the phonon dynamics, we performed time-dependent analysis by fitting the oscillating component $s(t)$ of the reflectivity signal. The fitting model consists of the sum of three damped cosines corresponding to the three main

modes, indexed i , of the Fourier spectrum, each characterized by its own amplitude A_i , frequency ν_i , phase φ_i and damping rate γ_i :

$$s(t) = \sum_{i=1}^3 A_i \cos(2\pi\nu_i t + \varphi_i) \exp(-\gamma_i t) \quad (1)$$

The oscillations are nicely reproduced [Fig. 6(e-h)] by this model in the temperature range 100 - 230 K. With this method we extracted the values of the frequencies, damping rates and initial phases of the three main phonons identified. Figure 7 displays these components independently for the two probe energies at 100 K. For the three modes, the results are almost similar. The contribution of the 2.5 THz phonon to reflectivity change at 0.83 eV appears to be π phase shifted compared to that at 1.72 eV. The three modes appear to be of cosine type (φ close to 0) indicating that immediately after photoexcitation the amplitude is maximum. This is characteristic of a displacive mechanism³⁴: the structural reorganisation induced by the laser excitation moves the system toward a new minimum position in the potential energy surface for this photoinduced ($D^0D^1D^0D^1$) state. This is associated with the displacive nature of the structural trapping, as intra- and intermolecular structure change, directly evidenced by femtosecond electron diffraction in the PF_6 derivative⁹.

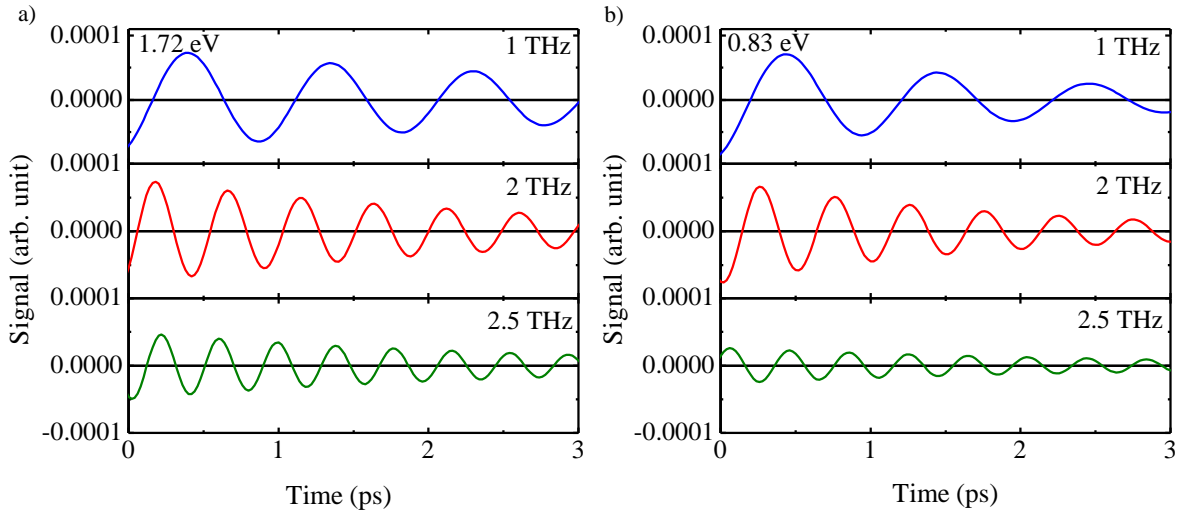


FIG. 7. (Color online) Oscillograms of the three main phonons at 100 K for a probe at 1.72 eV (a) and 0.83 eV (b).

A detailed study of the photoinduced dynamics was then performed by using the 1.46 eV pump and 1.72 eV probe for which the relative increase of reflectivity is larger between I and M phases and where the vibrations modes are better observed.

B. Response to different laser fluencies

First, we investigated the dependence of the photoresponse to excitation densities up to 4 times higher than those used in Ref. 5. Figure 8(a) shows selected data analysed as explained above and Fig. 8(b) shows the dependence of the frequencies of the three main modes with the pump fluency. These results indicate that there is very little, if any, dependence of the frequencies with the pump excitation density. This contrasts with photoexcitation process in systems like bismuth, in which the excited electrons are delocalized over the conduction band and the depopulation of the valence band leads to softening of the inter-atomic potential, due to thermalization of the electronic and phononic sub-systems³⁵⁻⁴⁰. As a consequence, the Bi-Bi dimerization mode softens with the excitation density. This is not the case in our study and this is an indication of the local nature of the structural trapping of the electronic excited state. This local trapping was theoretically introduced to explain the two-step dynamics⁶⁻⁹, which we will discuss in the last part of this paper.

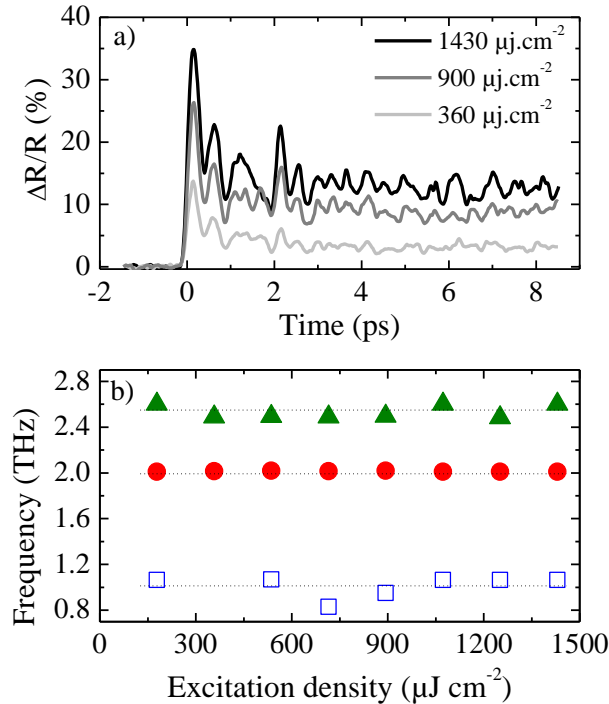


FIG. 8. (Color online) (a) Photoresponse of $(\text{EDO-TTF})_2\text{SbF}_6$ at 100 K for 1.46 eV pump and 1.72 eV probe at different fluencies. (b) Photon excitation density dependence of the phonon frequencies at 100 K.

In addition to the oscillating part discussed above, the photoinduced dynamics is also characterized by an important increase of reflectivity at 1.72 eV. Figure 9 shows the excitation density dependence of $\Delta R/R$ integrated on two different timescales: at the picosecond timescale, between 6.5 and 8.5 ps [Fig. 9(a)], and at the nanosecond timescale, between 2.3 and 3 ns [Fig. 9(b)]. On picosecond timescale the reflectivity appears to change linearly with excitation density and we could not detect any threshold manifesting nonlinear effects in $(\text{EDO-TTF})_2\text{SbF}_6$ despite spanning a broad excitation density range. Our measurements were performed with fluencies from $4 \mu\text{J}\cdot\text{cm}^{-2}$ to $1400 \mu\text{J}\cdot\text{cm}^{-2}$. This range starts from 10 times lower than the excitation density threshold determined for $(\text{EDO-TTF})_2\text{PF}_6$ ⁵, at around $50 \mu\text{J}/\text{cm}^2$, and extends to about 30 times higher, i. e., just before damage. On nanosecond timescale, $\Delta R/R$ shows oscillations with 100s ps period [inset of Fig. 9(b)]. These are very likely due to acoustic waves and are damped within 1 ns. Therefore, the averaging range from 2.3 to 3 ns does not take into account these oscillations. Similarly to the picoseconds timescale, the photoresponse exhibits a linear response with excitation density [Fig. 9(b)].

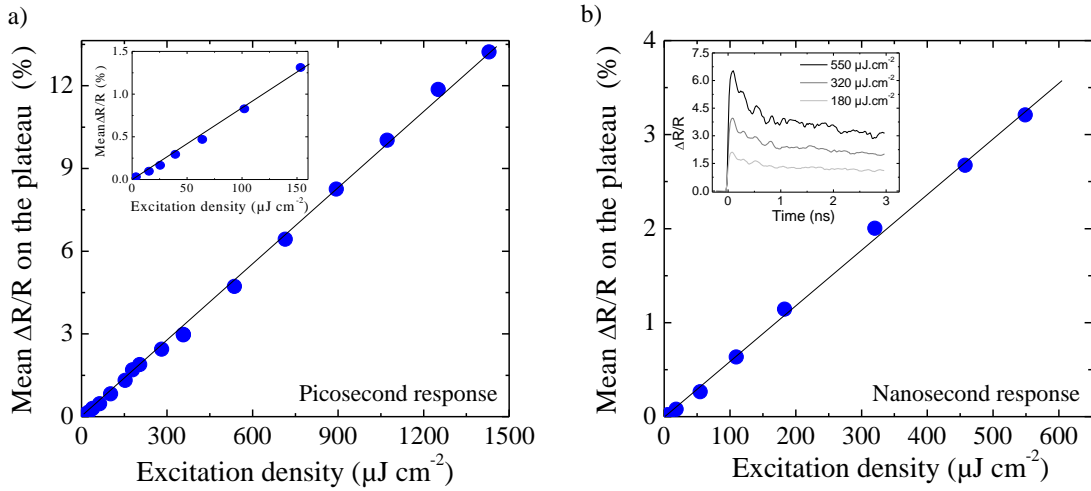


FIG. 9. (Color online) Plateau signal for 1.46 eV pump and 1.72 eV probe, integrated between 6.5 and 8.5 ps at 100 K (a). The blow up of the excitation densities under $150 \mu\text{J}\cdot\text{cm}^{-2}$ is in the inset. Plateau signal integrated between 2.3 and 3 ns (b). The inset shows the photoresponse at different excitation densities.

C. Temperature dependence

Time-resolved optical data were also collected at different temperatures and analyzed the same way. Figure 10(a) shows how frequencies of the main three modes change with

temperature. The modes around 1 and 2 THz exhibit a clear softening with temperature while that around 2.5 THz is more difficult to analyze because weak spectral weight above 190 K. Figure 10(b) shows the damping rate of the modes with temperature below 190 K.

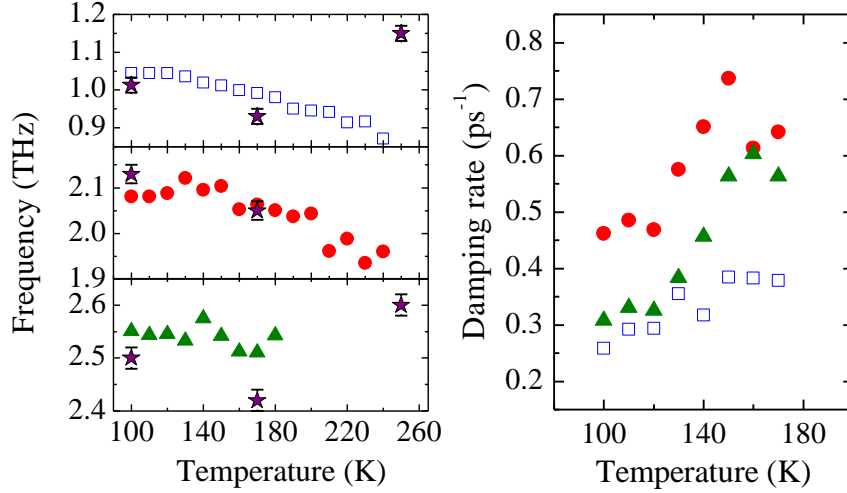


FIG. 10. (Color online) (a) Temperature dependence of frequencies for the 3 main modes at around 1 THz (□), 2 THz (●) and 2.5 THz (▲) from the fit model and by Raman spectroscopy (★) from 100 K to 240 K. (b) Temperature dependence of damping rate.

V. DISCUSSION

The results presented here for (EDO-TTF)₂SbF₆ can be compared with the experimental and theoretical reports on the isostructural (EDO-TTF)₂PF₆ for which a rich literature already exists. The photo-excitation of the initial charge-ordered I phase (D⁰D¹D¹D⁰) in the CT band drives a CT to the {D⁰D²D⁰D⁰} state which very rapidly relaxes locally to the (D⁰D¹D⁰D¹) state. This new local order is trapped by a structural reorganization involving different degrees of freedom. Femtosecond electron diffraction⁹ on (EDO-TTF)₂PF₆ revealed the important role of three main displacements: the bending of EDO-TTF molecules, the sliding of flat EDO-TTF molecules correlated to the sliding of the anion. The displacive nature of this local trapping drives the system towards a local minimum of the potential energy surface and these three different coordinates oscillate in a new potential. Since we observe three main modes we tentatively assign them to the motions observed by electron diffraction but it is difficult to attribute the vibrations observed to specific motions.

On picosecond timescale, the amplitude of the photoresponse changes linearly with excitation density of the pump laser [Fig. 9(a)], whereas the mode frequencies remain

unchanged [Fig. 8(b)]. These two features agree with a local nature of the initial process similarly with the PF₆ derivative⁶. In parallel, the frequencies of the observed modes reported in Fig. 10(a) differ from those measured at thermal equilibrium in the I phase. This indicates that the process observed do not correspond to an Impulsive Raman process. These modes are different too from those of the M phase and this is a spectroscopic evidence that the M phase is not formed on picosecond timescale. This is confirmed by the fact that $\Delta R/R$ remains negative at 0.83 eV [Fig. 6(d)] whereas it is positive in the thermal M phase [Fig. 3(a)]. We conclude that this state is similar to the transient intermediate state formed on the picosecond timescale in (EDO-TTF)₂PF₆ and tentatively assigned it to the local (D⁰D¹D⁰D¹) state⁶. Finally, this initial step, taking place at the molecular level, does not seem affected by bigger anion size as the photoresponse is similar for both compounds.

On the 100-picosecond timescale, (EDO-TTF)₂PF₆ exhibits a clear change of structure and charge revealed by the structural dynamics studied both by ultrafast vibrational spectroscopy⁸ and ultrafast electrons diffraction⁹. These changes unveil the formation of a state similar to the thermal M (D^{0.5}D^{0.5}D^{0.5}D^{0.5}) phase. They are accompanied by modification of the infrared spectroscopic fingerprint, approaching that of the M phase⁸. This is not the case in the present (EDO-TTF)₂SbF₆ compound, for which the $\Delta R/R$ at 0.83 eV remains clearly negative and of the same order of magnitude until 3 ns [Fig. 5], whereas it should be positive if the M phase was formed [Fig. 3(a)]. We could not detect any formation of the metallic state on the nanosecond timescale, but only a decay of this photoinduced state as shown in Fig. 5, even for excitation densities close to sample damage and higher than that used for (EDO-TTF)₂PF₆. We conclude that unlike (EDO-TTF)₂PF₆, (EDO-TTF)₂SbF₆ does not undergo conversion towards the M phase and shows exclusively local response to light excitation. With such local response, a saturation regime should be observed when the number of photons equals the number of molecules. However, the sample degradation occurs at 1500 $\mu\text{J}\cdot\text{cm}^{-2}$ (1 photon per 50 molecules). Therefore we are far from the saturation regime and this is consistent with the observed linear response. As the only structural difference between the two compounds is the larger size of SbF₆ anions resulting in a three times larger $\Delta V/V_{\text{HT}}$ during the I-M transition, we conclude that the phase transition towards the metallic phase is more difficult because it costs more elastic energy for the SbF₆ than the PF₆ derivative. It is established now that during the early stage of the photoinduced process, the volume does not change. The volume expansion, which is required for driving macroscopic phase change, typically occurs on an acoustic time-scale defined by the ratio between the laser penetration

depth and the speed of sound²¹. We note that the establishment of the M phase in the PF₆ derivative occurs only around 100 ps^{8,9}. Despite the occurrence of thermal phase transition in (EDO-TTF)₂SbF₆, the associated volume change is too large to be overcome during the photoinduced process and this prevents the formation of a macroscopic three dimensional M order. This picture is consistent with our study which indicates that the photoinduced transformation remains local in this compound.

V. SUMMARY

The counter-anion in the family of (EDO-TTF)₂XF₆ compounds has always been considered to be of prime importance in the thermal transition¹¹ and its role in the photoinduced transformation was evoked by recent time-resolved electron diffraction experiments. However, until now, the fundamental importance of its size in photoinduced phenomena was not discussed yet. In this work, we investigate the photoinduced transformation of the (EDO-TTF)₂SbF₆ derivative with a bigger counter anion. It acts as a negative pressure which increases the distance between chains and decreases the coupling between them. We observe that the photoinduced state is unambiguously of local nature as it is the case for the initial state. The major new finding is that (EDO-TTF)₂SbF₆ does not reach photoinduced M phase, which we rationalize with hindrance by the larger counter anions.

ACKNOWLEDGMENTS

This work was supported by the Institut Universitaire de France, the ANR (09-BLAN-0212), Région Bretagne (CREATE Ultimate 4146), Rennes Métropole and Europe (FEDER) and JSPS KAKENHI Grant Number 15K17901 and 26288035.

References :

*To whom correspondence should be addressed: marina.servol@univ-rennes1.fr

¹H. Cailleau, M. Lorenc, M. Buron-Le Cointe, M. Servol, M. Cammarata, E. Collet, Eur. Phys. J. Special Topics **222**, 1077-1092 (2013).

²H. Cailleau, T. Luty, S. Koshihara, M. Servol, M. Lorenc, M. Buron-Le Cointe, E. Collet, *Acta Phys. Polon. A* **121**, 297 (2012).

³K. Yonemitsu, K. Nasu, *Phys. Rep.* **465**, 1 (2008).

⁴K. Nasu, *Photoinduced Phase Transitions*, edited by K.Nasu (World Scientific, Singapore, 2004).

⁵M. Chollet, L. Guerin, N. Uchida, S. Fukaya, H. Shimoda, T. Ishikawa, K. Matsuda, T. Hasegawa, A. Ota, H. Yamochi, G. Saito, R. Tazaki, S.-ichi Adachi, S. Koshihara, *Science* **307**, 86 -89 (2005).

⁶K. Onda, S. Ogihara, K. Yonemitsu, N. Maeshima, T. Ishikawa, Y. Okimoto, X. Shao, Y. Nakano, H. Yamochi, G. Saito, S. Koshihara, *Phys. Rev. Lett.* **101**, 067403 (2008).

⁷Y. Matsubara, S. Ogihara, J. Itatani, N. Maeshima, K. Yonemitsu, T. Ishikawa, Y. Okimoto, S. Koshihara, T. Hiramatsu, Y. Nakano, H. Yamochi, G. Saito, and K. Onda, *Phys. Rev. B* **89**, 161102 (2014).

⁸N. Fukazawa, M. Shimizu, T. Ishikawa, Y. Okimoto, S. Koshihara, T. Hiramatsu, Y. Nakano, H. Yamochi, G. Saito, et K. Onda, *J. Phys. Chem. C* **116**, 5892 (2012).

⁹M. Gao, C. Lu, H. Jean-Ruel, L.C. Liu, A. Marx, K. Onda, S. Koshihara, Y. Nakano, X. Shao, T. Hiramatsu, G. Saito, H. Yamochi, R.R. Cooney, G. Moriena, G. Sciaini, and R.J.D. Miller, *Nature* **496**, 343 (2013).

¹⁰Y. Nakano, H. Yamochi, G. Saito, M. Uruichi, K. Yakushi, *J. Phys.: Conf. Ser.* **148**, 012007 (2009).

- ¹¹A. Ota, H. Yamochi, G. Saito, *J. Mater. Chem.* **12**, 2600-2602 (2002).
- ¹²S. Aoyagi, K. Kato, A. Ota, H. Yamochi, G. Saito, H. Suematsu, M. Sakata, M. Takata, *Angewandte Chemie* **116**, 3756-3759 (2004).
- ¹³K. Iwano and Y. Shimoi, *Phys. Rev. B* **77**, 075120 (2008).
- ¹⁴K. Iwano and Y. Shimoi, *Phys. Rev. Lett.* **110**, 116401 (2013).
- ¹⁵K. Onda, H. Yamochi, and S. Koshihara, *Acc. Chem. Res.* **47**, 3494 (2014).
- ¹⁶K. Yonemitsu and N. Maeshima, *Phys. Rev. B* **76**, 075105 (2007).
- ¹⁷G.-J. Linker, P.H.M. van Loosdrecht, P. van Duijnen, and R. Broer, *Chemical Physics Letters* **487**, 220 (2010).
- ¹⁸CrysAlis RED, Oxford Diffraction Ltd, Version 1.171.32.5 (2007).
- ¹⁹A. Altomare, M. C. Burla, M. Camalli, G. Cascareno, C. Giacovazzo, A. Guagliardi, A. G. G. Moliterni, G. Polidori, and R. Spagna, *J. Appl. Cryst.* **32**, 115 (1999).
- ²⁰G. M. Sheldrick, *Acta Cryst. A* **64**, 112 (2008).
- ²¹M. Lorenc, C. Balde, W. Kaszub, A. Tissot, N. Moisan, M. Servol, M. Buron-LeCointe, H. Cailleau, P. Chasle, P. Czarnecki, M.L. Boillot, E. Collet, *Phys. Rev. B* **85**, 054302 (2012).

²²CCDC-1023744 (250 K) and CCDC-1023745 (150 K) contain the supplementary crystallographic data for this paper. These data can be obtained free of charge via www.ccdc.cam.ac.uk/conts/retrieving.html (or from the Cambridge Crystallographic Data Centre, 12 Union Road, Cambridge CB21EZ, UK; fax: (+44) 1223-336033; or deposit@ccdc.cam.ac.uk).

²³O; Drozdova, K; Yakushi, K. Yamamoto, A. Ota, H. Yamochi, G. Saito, H. Tashiro, D.B. Tanner, *Phys. Rev. B* **70**, 075107 (2004).

²⁴O. Drozdova, K. Yakushi, A. Ota, H. Yamochi, and G. Saito, *Synthetic Metals* **133–134**, 277 (2003).

²⁵M. Maesato, Y. Nakano, X. Shao, Y. Yoshida, H. Yamochi, G. Saito, A. Moreac, J.-C. Ameline, E. Collet, M. Uruichi, and K. Yakushi, *J. Phys.: Conf. Ser.* **148**, 012004 (2009).

²⁶H. Hahn, in *Proceedings of the Symposium on Inelastic Scattering of Neutrons, International atomic energy agency, 1965*, p. 279.

²⁷D. Bormann, J.L. Sauvajol, C. Goze, F. Rachdi, A. Moreac, A. Girard, L. Forro, and O. Chauvet, *Phys. Rev. B* **54**, 14139 (1996).

²⁸P. Ranzieri, M. Masino, A. Girlando, and M.-H. Lemée-Cailleau, *Phys. Rev. B* **76**, 134115 (2007).

²⁹C. Katan, P.E. Blöchl, P. Margl, and C. Koenig, *Phys. Rev. B* **53**, 12112 (1996).

³⁰H. Uemura and H. Okamoto, *Phys. Rev. Lett.* **105**, 258302 (2010).

- ³¹Y. Kawakami, S. Iwai, T. Fukatsu, M. Miura, N. Yoneyama, T. Sasaki, and N. Kobayashi, *Phys. Rev. Lett.* **103**, 066403 (2009).
- ³²M. Cammarata, R. Bertoni, M. Lorenc, H. Cailleau, S. Di Matteo, C. Mauriac, S.F. Matar, H. Lemke, M. Chollet, S. Ravy, C. Laulhé, J.-F. Létard, and E. Collet, *Phys. Rev. Lett.* **113**, 227402 (2014).
- ³³K. Onda, S. Ogihara, T. Ishikawa, Y. Okimoto, X. Shao, H. Yamochi, G. Saito, and S. Koshihara, *J. Phys.: Condens. Matter* **20**, 224018 (2008).
- ³⁴H.J. Zeiger, J. Vidal, T.K. Cheng, E.P. Ippen, G. Dresselhaus, and M.S. Dresselhaus, *Phys. Rev. B* **45**, 768 (1992).
- ³⁵M.F. DeCamp, D.A. Reis, P.H. Bucksbaum, and R. Merlin, *Phys. Rev. B* **64**, 092301 (2001).
- ³⁶M. Hase, M. Kitajima, S. Nakashima, et K. Mizoguchi, *Phys. Rev. Lett.* **88**, 067401 (2002).
- ³⁷É.D. Murray, D.M. Fritz, J.K. Wahlstrand, S. Fahy, and D.A. Reis, *Phys. Rev. B* **72**, 060301 (2005).
- ³⁸D.M. Fritz, D.A. Reis, B. Adams, R.A. Akre, J. Arthur, C. Blome, P.H. Bucksbaum, A.L. Cavalieri, S. Engemann, S. Fahy, R.W. Falcone, P.H. Fuoss, K.J. Gaffney, M.J. George, J. Hajdu, M.P. Hertlein, P.B. Hillyard, M. Horn-Von Hoegen, M. Kammler, J. Kaspar, R. Kienberger, P. Krejcik, S.H. Lee, A.M. Lindenberg, B. McFarland, D. Meyer, T. Montagne, É.D. Murray, A.J. Nelson, M. Nicoul, R. Pahl, J. Rudati, H. Schlarb, D.P. Siddons, K. Sokolowski-Tinten, T. Tschentscher, D. Von Der Linde, and J.B. Hastings, *Science* **315**, 633 (2007).

³⁹K. Sokolowski-Tinten, C. Blome, J. Blums, A. Cavalleri, C. Dietrich, A. Tarasevitch, I. Uschmann, E. Förster, M. Kammler, M. Horn-von-Hoegen, and D. von der Linde, *Nature* **422**, 287 (2003).

⁴⁰W. Lu, M. Nicoul, U. Shymanovitch, A. Tarasevitch, M. Kammler, M. Horn von Hoegen, D. von der Linde, K. Sokolowski-Tinten, in *Ultrafast Phenomena XVII*, edited by M. Chergui, D. Jonas, E. Riedle, R. Schoenlein, A. Taylor (Oxford University Press, Oxford, 2011), p. 314.