



HAL
open science

Anionic ordering and thermal properties of $\text{FeF}_3 \times 3\text{H}_2\text{O}$

Mario Burbano, Mathieu Duttine, Olaf Borkiewicz, Alain Wattiaux, Alain Demourgues, Mathieu Salanne, Henri Groult, Damien Dambournet

► **To cite this version:**

Mario Burbano, Mathieu Duttine, Olaf Borkiewicz, Alain Wattiaux, Alain Demourgues, et al.. Anionic ordering and thermal properties of $\text{FeF}_3 \times 3\text{H}_2\text{O}$. *Inorganic Chemistry*, 2015, 14 (19), pp.9619-9625. 10.1021/acs.inorgchem.5b01705 . hal-01212342

HAL Id: hal-01212342

<https://hal.science/hal-01212342v1>

Submitted on 24 Nov 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Anionic Ordering and Thermal Properties of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$

Mario Burbano,^{1,2,3} Mathieu Duttine,² Olaf Borkiewicz,⁴ Alain Wattiaux,² Alain Demourgues,² Mathieu Salanne,¹ Henri Groult,¹ and Damien Dambournet.^{1}*

¹ Sorbonne Universités, UPMC Univ Paris 06, CNRS, Laboratoire PHENIX, Case 51, 4 place Jussieu, F-75005 Paris, France.

² CNRS, Univ Bordeaux, ICMCB, UPR 9048, F-33600 Pessac, France.

³ Réseau sur le Stockage Electrochimique de l'Energie (RS2E), FR CNRS 3459, 80039 Amiens Cedex, France.

⁴ X-ray Science Division, Advanced Photon Source, Argonne National Laboratory, Argonne, Illinois, USA.

ABSTRACT. Iron fluoride tri-hydrate can be used to prepare iron hydroxyfluoride with the Hexagonal-Tungsten-Bronze (HTB) type structure, a potential cathode material for batteries. To understand this phase transformation, a structural description of $\beta\text{-FeF}_3\cdot 3\text{H}_2\text{O}$ is first performed by means of DFT calculations and Mössbauer spectroscopy. The structure of this compound consists of infinite chains of $[\text{FeF}_6]_n$ and $[\text{FeF}_2(\text{H}_2\text{O})_4]_n$. The decomposition of $\text{FeF}_3\cdot 3\text{H}_2\text{O}$ induces a collapse and condensation of these chains, which lead to the stabilization, under specific conditions, of a hydroxyfluoride network $\text{FeF}_{3-x}(\text{OH})_x$ with the HTB structure. The release of H_2O and HF was monitored by thermal analysis and physical characterizations during the decomposition of $\text{FeF}_3\cdot 3\text{H}_2\text{O}$. An average distribution of $\text{FeF}_4(\text{OH})_2$ distorted octahedra in $\text{HTB-FeF}_{3-x}(\text{OH})_x$ was obtained subsequent to the thermal hydrolysis/olation of equatorial anionic positions involving F^- and H_2O . This study provides a clear understanding of the structure and thermal properties of $\text{FeF}_3\cdot 3\text{H}_2\text{O}$, a material that can potentially bridge the recycling of pickling sludge from the steel industry by preparing battery electrodes.

KEYWORDS. Metal fluoride hydrate, thermal analysis, anionic ordering, HTB, cathode.

1. INTRODUCTION

Among the potential new positive electrode materials for batteries (Na^+ , Li^+), iron fluoride combines very appealing redox properties such as a high theoretical capacity (237 mAh/g per lithium), a relatively high voltage (around 3.1-3.3V), and a good thermal stability.¹ However, if this material is to be deployed in practical applications, its synthesis must meet rigorous cost and environmental criteria.² In these respects, recent work has shown that it is possible to recycle the acid and metal by-products from the steel industry by precipitating $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ from pickling liquor.^{3,4} Subsequent studies by Sanghvi *et al.*⁵ proposed and demonstrated the use of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ as a precursor for battery cathodes. In their work, $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ was allowed to crystallize at room temperature from the spent liquor for a week and upon thermal treatment it yielded the rhombohedral form of iron fluoride ($\alpha\text{-FeF}_3$), which when used as an electrode showed superior cycling ability compared to a commercial product. As indicated by the authors, the yield of 27% based on Fe from the hydrate precipitation remains to be improved, which could likely be achieved by thermal activation. Further enhancements of the electrochemical properties of the end product are also likely to result from an optimized decomposition of $\beta\text{-FeF}_3 \cdot 3\text{H}_2\text{O}$. It is thus necessary to glean a better understanding of the thermal properties of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ if it is to be a viable precursor for battery cathodes.

Several procedures have been developed to prepare iron fluoride from the thermal decomposition of $\beta\text{-FeF}_3 \cdot 3\text{H}_2\text{O}$ (henceforth $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$). Depending on the protocol, different compounds have been obtained ranging from amorphous to various forms of crystallized compounds, thus emphasizing a complex thermal decomposition path.⁶⁻⁸ Li *et al.*⁹ showed that the thermal decomposition of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ in an ionic liquid can yield $\text{FeF}_3 \cdot 0.33\text{H}_2\text{O}$ with the hexagonal-tungsten-bronze (HTB)¹⁰ type structure. The same authors attempted to describe the structural relationship between the two structures. Nevertheless, the structure of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ depicted by the authors is unreasonable with

heavily distorted $\text{FeF}_4(\text{H}_2\text{O})_2$ octahedra probably due to an uncorrected choice of crystallographic origin during crystal structure drawing.

In the present article, we investigate the crystal structure of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ by means of Rietveld analysis of x-ray diffraction data, DFT calculations and Mössbauer spectroscopy. The results point toward a structure featuring ordered FeF_6 and $\text{FeF}_2(\text{H}_2\text{O})_4$ octahedra as opposed to the average $\text{FeF}_4(\text{H}_2\text{O})_2$ crystal unit. A comprehensive study of the thermal behavior of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ was also undertaken using thermogravimetric analysis combined with mass spectrometry.

2. EXPERIMENTAL AND COMPUTATIONAL METHODS

Synthesis of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$. $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ was precipitated from an aqueous solution containing Fe^{3+} nitrate nonahydrate ($\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$) and hydrofluoric acid (HF, Rectapur, 40%). 0.042 mol of Fe^{3+} salt was dissolved in 42 mL of distilled water. 0.168 mol of HF, corresponding to a F/Fe molar ratio equals to 4, was added to the solution. The precipitation was thermally assisted by microwave heating performed in a microwave-accelerated reaction system MARS5 (CEM corporation) operating at 2.45 GHz with a power supply of 900 watts. As previously reported, Ref. ¹¹ the microwave-assisted synthesis consists of two successive steps including activation and drying processes. For the former, the solution was heated up to the synthesis temperature (90 °C) within five minutes, and further kept for 30 min. Thereafter, the solution was cooled down to room temperature. The drying step was performed at 90°C under nitrogen gas stream and primary vacuum (~500 mbar). The obtained powder was washed by ultrafiltration using ethanol and nitrogen gas flow. Finally, the powder was outgassed at 90°C under vacuum for two hours.

Decomposition under self-generated atmosphere. In a typical procedure, 0.5 g of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ was placed in an alumina crucible. To obtain a self-generated atmosphere produced during the decomposition process of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$, the crucible was tightly enrolled in an aluminum foil. The sample

was then placed in a tubular oven which was progressively heated at 5 °C/ min under air and left at the desired temperature for two hours. Thereafter, the oven was cool down to RT and the sample was recovered.

Thermal analyses. Thermogravimetric analysis (TGA) was performed using Setaram Setsys evolution that was coupled with a mass spectrometer (MS) (Pfeiffer Ominstar) allowing the detection of HF and water departures. Samples were heated from room temperature up to 600°C under helium atmosphere (heating rate 5°C/min).

X-ray diffraction (XRD) analysis. Powder XRD patterns were recorded on PANalytical X'Pert (Co-K α or Cu-K α_1 radiations) diffractometers in a Bragg–Brentano geometry (θ – 2θ). Structural analysis of was performed using Le Bail and Rietveld methods as implemented in the FULLPROF software.¹²

Mössbauer spectroscopy. Measurements were performed at room temperature using a constant acceleration Halder type spectrometer with a room temperature ⁵⁷Co source in transmission geometry. The velocity was calibrated using pure α -Fe as the standard material. Mossbauer spectra were reconstructed using the WinNormos software.¹³

Pair Distribution Function (PDF) analysis. Samples were packed in Kapton capillaries. High energy X-ray data were collected at the 11-ID-B station at the Advanced Photon Source (Argonne National Laboratory). After corrections (background and Compton scattering), PDFs were extracted from the data using PDFgetX2 software.¹⁴ Refinements of the PDF data were performed using PDFgui.¹⁵

Computational methods. The structure and total energy of the bulk compounds FeF₃·3H₂O and FeF₃-HTB, as well as, the defects in FeF₃-HTB cells were studied using the plane-wave DFT implementation found in the VASP code.^{16,17} The Perdew-Burke-Ernzerhof (PBE) GGA exchange-correlation functional was supplemented by the Dudarev $+U$ correction in order to describe correctly the strongly correlated Fe 3d states. A value of $U_{\text{Fe}(d)} = 5.3$ eV was used as is the case for the iron oxyfluorides studied in the Materials Genome project.¹⁸ Valence-core interactions were represented by means of the projector-

augmented wave (PAW) approach.^{19,20} In the case of the 12 FeF₃·3H₂O configurations investigated, structural optimizations were performed the VASP tag ISIF = 3, that allows the shape, volume and ionic positions to be relaxed. The optimal FeF₃-HTB structure was obtained by performing multiple relaxations at constant volume in order to fit to the Murnaghan²¹ equation of state. This method avoids the problems of Pulay stress and changes in basis set which are intrinsic to plane wave calculations. A plane wave cut-off of 500 eV was used throughout all the calculations, with well-converged k-point sampling for each system, i.e. 4x4x6 for β-FeF₃·3H₂O and 4x2x4 for FeF₃-HTB, both Γ-centred. All calculations were spin polarized and were initialized assuming a high-spin ferromagnetic ordering for the Fe ions.²² Structural optimizations were considered converged when the force on every ion was less than 0.01 eV/ Å.

3. RESULTS AND DISCUSSION

3.1. Structural analysis of FeF₃·3H₂O. Iron fluoride tri-hydrate was synthesized using a precipitation method performed in aqueous medium by a microwave-assisted hydrothermal process. The yield of the reaction was ca. 85% based on Fe. This method could be easily applied to prepare iron fluoride from steel pickling liquor. The prepared solid exhibited large micrometric particles with irregular shape (**Figure S1** in Supplementary Information). The phase purity was confirmed by indexation of the X-ray diffraction pattern using a tetragonal symmetry corresponding to iron fluoride tri-hydrate FeF₃·3H₂O. The crystal structure of FeF₃·3H₂O was studied by Rietveld analysis of the XRD pattern (**Figure 1**). Full pattern profile refinement of the XRD pattern yielded the following unit cell parameters a=b=7.8327(2) Å and c=3.8754(1) Å, in good agreement with literature data.²³

Rietveld analysis was performed using a structural model based on the aluminum analogue AlF₃·3H₂O^{24,25} (Space group : P4/n). The final reliability structural factor was satisfactory with R_{Bragg} = 7.7%. Structural parameters are gathered in Supporting Information (**Table S1**).

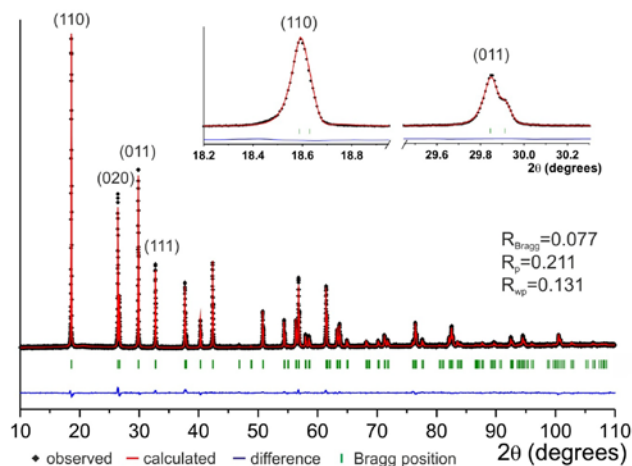


Figure 1. Rietveld refinement of the x-ray diffraction pattern (CoK α source) of FeF₃·3H₂O.

The refinement confirms that FeF₃·3H₂O is isostructural to the Al-homologue, whose structure is built from infinite chains of corner-sharing FeF₄(H₂O)₂ slightly distorted octahedra held by structural hydrogen-bonds from water (Figure 2a). The axial F atoms displayed a Fe-F distance of 1.920(4) and 1.955(4) Å while the equatorial positions show distances of 1.9947(13) Å. The equatorial positions of the octahedra (8g Wyckoff site) are predicted by the crystal symmetry to be statistically occupied by two fluoride and two water molecules, yielding FeF₄(H₂O)₂ octahedra as the average building block. However, this average picture does not enable a full description of the local Fe³⁺ environment as anion ordering can occur at this site.

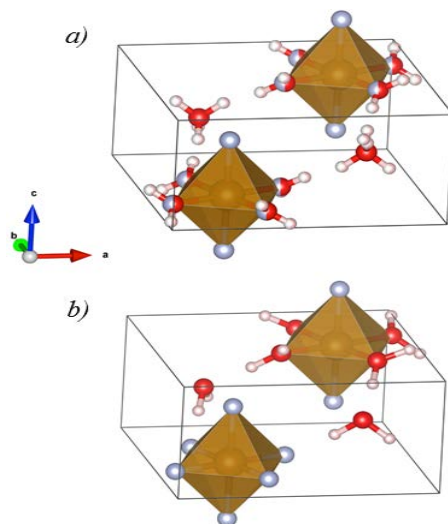


Figure 2. a) Structure of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ with partial occupancies in the equatorial positions of the octahedra (8g Wyckoff site). b) Lowest energy configuration obtained by atomic simulation highlighting an anionic ordering.

In order to establish the possible speciation of Fe^{3+} , we carried out atomistic simulations of all the possible configurations as given by the symmetry of the cell. These were generated by the Site Occupancy Disorder (SOD) program by Grau-Crespo et al.²⁶ In this case, SOD used the symmetry operations of the space group P4/n of the cell to generate 12 unique configurations that account for the partially occupied equatorial positions by fluoride and water molecules. These 12 configurations correspond to the occurrence of different anionic environments in Fe^{3+} octahedra such as $\text{FeF}_{6-x}(\text{H}_2\text{O})_x$, with $0 \leq x \leq 4$. Each of these configurations was subsequently relaxed using Density Functional Theory (DFT) in order to find the most stable (See Computational Methods for more details). The resulting energies along with the probabilities of formation at 300 K for the 12 configurations (**Table S2**) unambiguously pointed toward a unique stable configuration, namely configuration 1 (**Figure 2b**). The predicted structure parameters and bond lengths of this configuration are given in **Table S3**. From **Figure 2b** it is clear that there exists anionic ordering in this structure because in this case various anions, F^- and H_2O are segregated into the equatorial positions, revealing the existence of two types of Fe^{3+} octahedra in equal proportions, FeF_6 and $\text{FeF}_2(\text{H}_2\text{O})_4$, which are stacked along the c-axis in chains.

To get further confirmation of the existence of the extended FeF_6 and $\text{FeF}_2(\text{H}_2\text{O})_4$ chains along the c-axis, we generated a $1 \times 1 \times 2$ supercell for configuration 1 and a second cell of the same dimensions, but with an alternating stacking of the Fe octahedra along the c-axis as shown in **Figure 3a** and **Figure 3b**, respectively. These two different configurations were subsequently relaxed using DFT in order to obtain their energies; the results (per formula unit) indicate that the system with chains of either FeF_6 or $\text{FeF}_2(\text{H}_2\text{O})_4$ octahedra along the c-axis has a lower energy (-65.68954 eV) compared to that in which

the FeF_6 or $\text{FeF}_2(\text{H}_2\text{O})_4$ octahedra alternate along this direction (-65.09279 eV). This energy difference and the large distortions undergone in the system with alternating octahedra indicates that $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ is likely to adopt a configuration like that shown in **Figure 3c**.

The local environment of Fe^{3+} in $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ was also probed experimentally using Mössbauer spectroscopy. In order to compare the different structural models predicted either by the crystal symmetry or by DFT calculations, the Mössbauer spectrum was reconstructed using one or two different Fe^{3+} environments (**Figure 3d**). The best fit was provided using the two different Fe^{3+} environments in agreement with DFT calculations. In particular, it enables to account for the asymmetric character of the doublet. The resulting Mössbauer parameters are presented in **Table 1**. The two signals display similar isomer shift values, *e.g.* 0.45 mm/s, characteristic of trivalent iron in a six-fold coordination mode. The relative intensity indicated that the two signals are in equal proportion, which is in agreement with the predictions from DFT calculations. Moreover, both signals differed only by their quadrupole splitting ΔE_Q value, which reflects the distortion of the Fe^{3+} octahedral related to various anionic environment. The quadrupole splitting arises mainly from the lattice contribution to the electric field gradient (EFG) through the crystal field produced by ligands at the ^{57}Fe nucleus. Therefore, the FeF_6 environment likely shows a lower quadrupole splitting than $\text{FeF}_2(\text{H}_2\text{O})_4$. As a result, signals 1 and 2 were assigned to FeF_6 and $\text{FeF}_2(\text{H}_2\text{O})_4$, respectively (**Table 1**).

Table 1. ^{57}Fe Mössbauer parameters of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ obtained from the reconstruction of spectra shown in Figure 3d and their assignments. δ = isomer shift relative to α -iron standard, ^{57}Co (Rh) source; ΔE_Q = quadrupole splitting; Γ = lorentzian linewidth.

Signals	Fe^{3+} [6] (1)	Fe^{3+} [6] (2)
δ (mm/s)	0.44(1)	0.45 (1)
ΔE_Q (mm/s)	0.50(1)	0.69(1)
Γ (mm/s)	0.29(1)	0.28(1)

Area (%)	49.3(5)	50.7(5)
Assignments	FeF ₆	FeF ₂ (H ₂ O) ₄

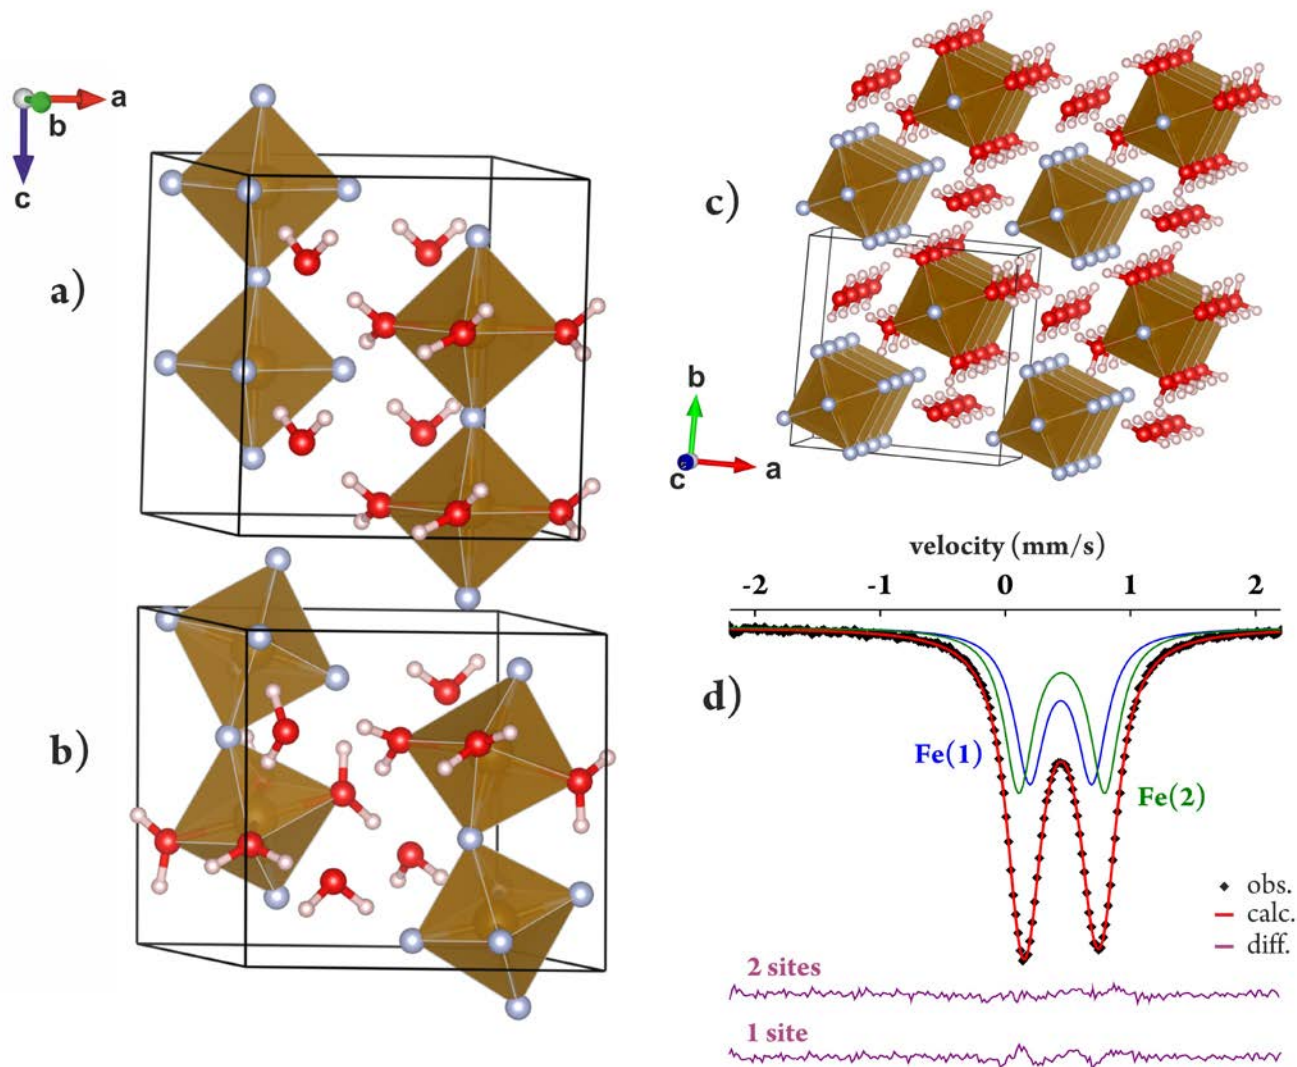


Figure 3. a) $1 \times 1 \times 2$ supercell of the lowest energy configuration (configuration 1). b) Supercell with alternating FeF₆ and FeF₂(H₂O)₄ octahedra along the c-axis. c) Extended cell of the lowest energy configuration. d) Mössbauer spectrum of β -FeF₃·3H₂O reconstructed using two Fe³⁺ signals, Fe(1) (blue) and Fe(2) (green). The difference between the observed and calculated values is represented as violet lines.

3.2. Thermal analysis of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$. The thermal behavior of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ was studied by means of thermogravimetric analysis (TGA) coupled with a mass spectrometer under helium atmosphere (**Figure 4**). The results of this analysis reveal two distinct steps in the decomposition of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ as observed in the change of slope of the TGA curve. These steps were assigned to the stabilization of HTB-structured $\text{FeF}_3 \cdot (\text{H}_2\text{O})_{0.33}$ and to $\alpha\text{-FeF}_3$ at high temperature, respectively.


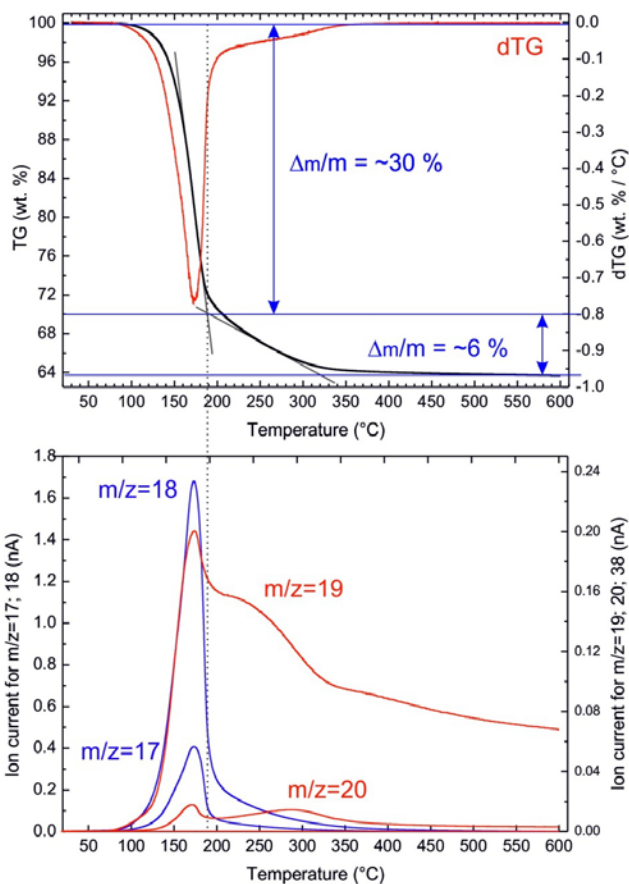


Figure 4. Thermogravimetric (top) and mass spectrometry (bottom) analyses of $\beta\text{-FeF}_3 \cdot 3\text{H}_2\text{O}$ performed under He.


The analysis by mass spectrometry emphasized a complex thermal decomposition process with the detection of gaseous hydrofluorhydric acid (HF) in addition to the expected water vapor. The monitoring of the ionic curves of the mass fragments $m/z = 17$ (OH^+), 18 (H_2O^+), 19 (F^+) and 20 (HF^+) enabled a better understanding of the thermal decomposition process of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$. The first

thermogravimetric event occurred within the 30-240 °C range at a DTG maximum around 170°C leading to 30 %wt loss (**Figure 4**. bottom). During this step, the mass spectrometer detected the release of H₂O and HF indicating concomitant dehydration and hydrolysis reactions. The detection of HF emphasized a partial replacement of Fe-F by Fe-OH bonds,²⁷ which indicates that this initial stage of the process likely involved the stabilization of a hydroxylated HTB type structure rather than a pure fluoride. During this step, the release of the structural water from FeF₃·3H₂O induced the collapse of the structure followed by the concomitant condensation of the 1D chains of [FeF₂(H₂O)₄]_n and [FeF₆]_n with subsequent dehydration and hydrolysis as follows:



The second step occurred within the 240-440 °C temperature range and led to 6% wt loss. The mass spectrometry data indicated the continuous release of both water and HF. The release of H₂O arises from the removal of structural water and dehydroxylation reaction of the HTB type structure. The departure of HF might result from the continuous hydrolysis of the structure during its transformation toward α-FeF₃.

The rate of hydrolysis was quantified by the analysis of the XRD pattern obtained from the powder recovered after the TGA measurement, i.e. up to 600°C. Rietveld analysis (**Figure S2**) led to an estimated molar percentage of 16% and 84% for Fe₂O₃ and α-FeF₃, respectively. The overall reaction that takes place during the thermal decomposition of FeF₃·3H₂O can thus be summarized as follows:



The theoretical weight loss associated with the above reaction was $\Delta m/m * 100 = 35.5\%$, in good agreement with the experimental data (36.3%). This weight loss is close to that calculated for a simple dehydration process: $\text{FeF}_3 \cdot 3\text{H}_2\text{O} \rightarrow \text{FeF}_3 + 3\text{H}_2\text{O}$ (wL: 32.4%) which might cause misinterpretation.

This is due to the fact that exchanges of F/OH only slightly affect the mass variation and thus cannot be probed properly by using thermogravimetric analysis alone.²⁷

3.3. Optimized decomposition process of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ The thermal analysis of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ indicated that this compound can be used as a precursor for the preparation of the HTB framework, a potential cathode material for batteries.¹¹ However, it also revealed that the HTB phase exhibits a narrow range of stability with respect to temperature since the decomposition process can yield $\alpha\text{-FeF}_3$. The range of existence of intermediate compositions/structures can be extended by means of the self-generated atmosphere method,²⁸ where the decomposition of the metal fluoride hydrate takes place in a closed container.

We tested this strategy by performing two $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ decompositions at 130 °C for two hours, one under air and another under a self-generated atmosphere (See experimental section for details). X-ray diffraction analysis (**Figure 5**) showed that the sample decomposed under an air atmosphere (blue) is amorphous. A combination of Pair Distribution Function and Mossbauer spectroscopy has revealed that the sample decomposed under air consisted of a phase mixture of the HTB and $\alpha\text{-FeF}_3$.⁸ In contrast, the use of the self-generated atmosphere led to the stabilization of a pure and well crystallized compound whose pattern was indexed with an orthorhombic symmetry characteristic of the HTB type structure.

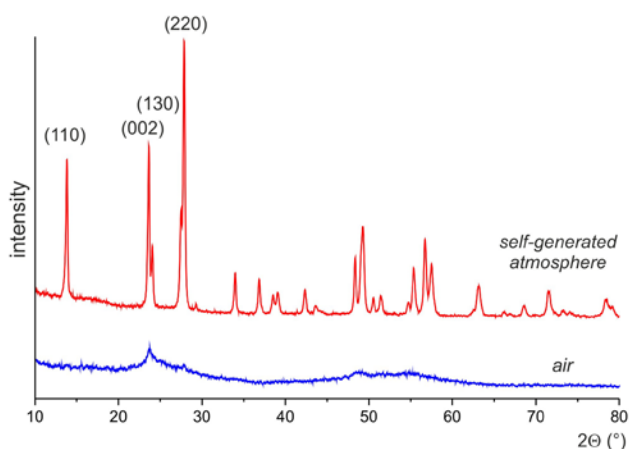


Figure 5. X-ray diffraction powder patterns of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ decomposed at 130°C under air (for 2 hours) with and without the self-generated atmosphere method.

The decomposition of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ under self-generated atmosphere was monitored by high-energy x-ray diffraction starting from low temperature, i.e. 100°C , to 130°C (**Figure 6**). Under these conditions, $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ readily decomposed into the HTB-type structure at $T > 100^\circ\text{C}$ and is obtained as a single phase at ca. $T = 130^\circ\text{C}$. Extending the decomposition process within the temperature range of 130 to 220°C still enabled the stabilization of the HTB-type structure showing that this condition clearly allows stabilizing intermediate phases.

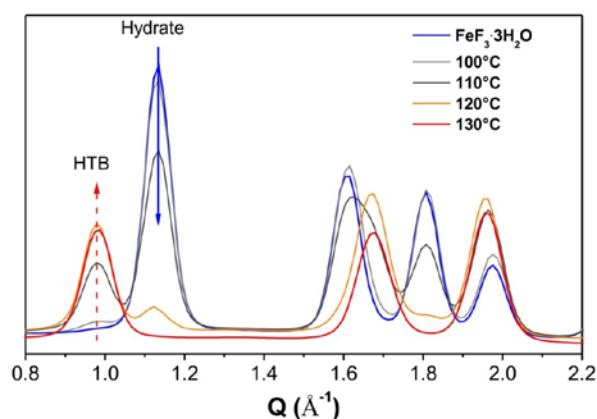


Figure 6. High energy X-ray diffraction powder patterns of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ decomposed at different temperatures under self-generated atmosphere.

3.4. Structural characterization of the HTB framework. Similarly to our previous study on amorphous FeF_3 , structural insight of the HTB phase was obtained by the Pair Distribution Functions and Mössbauer spectroscopy.⁸

The refinement of the PDF using the real space method confirms that the phase is pure without any amorphous component. Thus, the refinement of the PDF using HTB-type structure provides a good fit to the data (**Figure 7**).

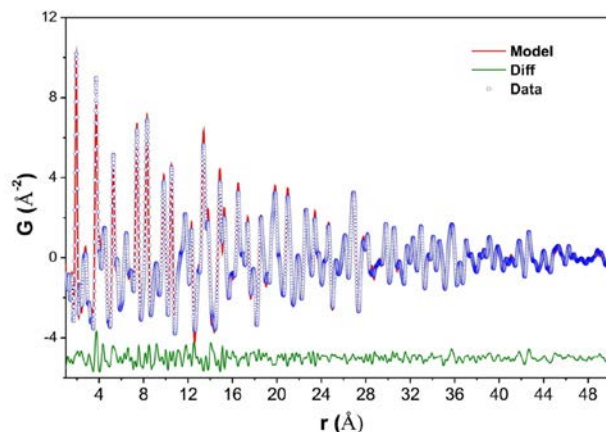


Figure 7. Refinement of the PDF of the phase prepared by thermal decomposition of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ decomposed at 130°C under self-generated atmosphere.

Crystal parameters (**Table S4**) reveal a broad distribution of inter-atomic distances that range from 1.883 to 1.986 Å and larger unit cell parameters which is due to the presence of OH groups partially substituting fluoride. Samples prepared at higher temperatures, i.e. $130 < T \leq 220^\circ\text{C}$, displayed similar crystal parameters characteristic of an hydroxyfluoride composition (**Table S4**), which suggests that the temperature only slightly impacts the rate of hydrolysis. The presence of OH groups was further confirmed by ^{57}Fe Mössbauer spectroscopy. The spectrum obtained (**Figure 8**) may be analyzed using distributions of both isomer shift and quadrupole splitting, *i.e.* the sum of quadrupole doublets with lorentzian shape (linewidth 0.26 mm/s), isomer shift ranging from 0.41 to 0.45 mm/s and different quadrupole splitting values, due to the presence of oxygen in the vicinity of Fe^{3+} . Furthermore, this shows that the Fe^{3+} ions exhibited different types of anionic environments with different F/OH ratios and heterogeneous inter-atomic distances in the $\text{FeF}_{6-x}(\text{OH})_x$ octahedra.

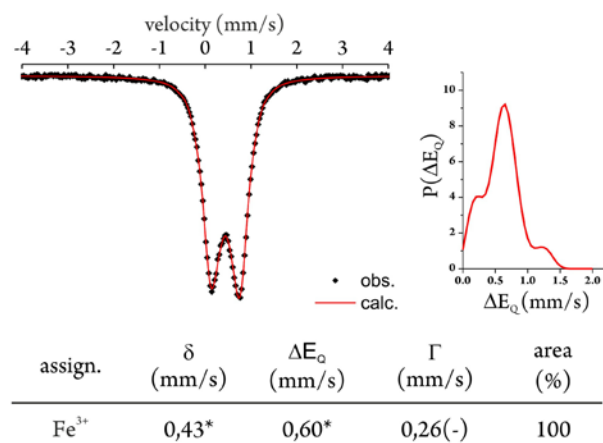


Figure 8. ^{57}Fe Mössbauer spectra of HTB- $\text{FeF}_{3-x}(\text{OH})_x$ hydroxyfluoride. Right panel: Quadrupole splitting distributions. ^{57}Fe Mossbauer parameters obtained from the reconstruction of spectra shown in left. * Average value

Thermal analysis (**Figure S3**) performed on the hydroxyfluoride revealed a combined departure of HF and H_2O at $T > 130^\circ\text{C}$, thus preventing the determination of an accurate OH content. Nevertheless, the chemical composition of the hydroxyfluoride phase obtained by decomposition of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ is close to $\text{FeF}_{2.2}(\text{OH})_{0.8}$.²⁷ This trend is also supported by the hydrolysis rate deduced by Rietveld analysis/TGA (cf. Eq.2, and **Figures S2** and **S3**). Then, in as-obtained HTB Fe hydroxyfluoride, the average octahedron is associated to the following chemical formulae $\text{FeF}_4(\text{OH})_2$. The release of H_2O and HF during the decomposition of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ with two kind of octahedra FeF_6 and $\text{FeF}_2(\text{H}_2\text{O})_4$ forming infinite chains leads to an average distribution of $\text{FeF}_4(\text{H}_2\text{O})_2$ distorted octahedra in HTB- $\text{FeF}_{3-x}(\text{OH})_x$ consecutive to the thermal ololation of equatorial anions position involving F/ H_2O .

3.5. Discussion on the decomposition of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ into HTB- $\text{FeF}_{3-x}(\text{OH})_x$ The structure of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ was found to be built from infinite chains of $[\text{FeF}_6]_n$ and $[\text{FeF}_2(\text{H}_2\text{O})_4]_n$ held by water molecules. The stabilization from the tri-hydrate phase toward the HTB type structure points out two features: (i) the role of the atmosphere to favor the formation of the HTB type structure and (ii) the hydrolysis occurring during the collapse of the $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ phase.

The decomposition of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ toward the HTB structure implies the concomitant condensation of $[\text{FeF}_6]_n$ and $[\text{FeF}_2(\text{H}_2\text{O})_4]_n$ chains yielding an hydroxyfluoride $\text{FeF}_{3-x}(\text{OH})_x$ network. Very likely, water vapor produced by the self-generated atmosphere process favors the formation of the HTB type structure. Nevertheless, the generation of OH groups during this process might also play a role in stabilizing the HTB structure at the expense of the distorted ReO_3 type structure ($\alpha\text{-FeF}_3$). To test this hypothesis, DFT simulations were used to calculate the formation energies of OH^- substitutions on the F^- anion sublattice in both the HTB and the distorted ReO_3 type structures. These energies were calculated from the energies of the relaxed cells for the pure and substituted systems (See Computational Methods). The converged cells are presented in **Figure 9**. The four different anion positions in the HTB cell are labeled F1, F2, F3 and F4; the distorted ReO_3 structure displays one anionic site only. The DFT calculations predict bond lengths of ca. 1.960 and 1.957 Å for the Fe-F distances of the HTB (**Table S5**) and distorted ReO_3 -type structures, respectively, which agree with experimental data.²⁹ The formation energies of single and double OH^- substitutions on the F^- anion sublattice in both the HTB and distorted ReO_3 -type structure are presented in **Table 3** using Kröger-Vink notation, e.g. OH_F represents a OH substitution for F^- . The results show that OH^- substitution for F^- is more favorable in all the different F sites of the HTB-type structure than in ReO_3 -structured FeF_3 . This highlights the need for a self-generated atmosphere in the stabilization of HTB- FeF_3 from $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$, because, as these values indicate, an uncontrolled reaction is likely to yield fluoride ($\alpha\text{-FeF}_3$) and oxide phases as suggested by experimental observations.⁵

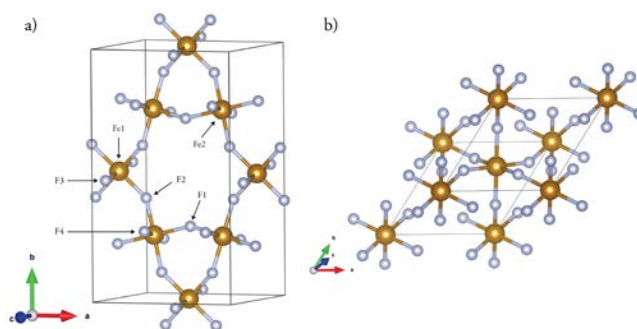


Figure 9. Converged structures of the FeF_3 -HTB (a) and (b) α - FeF_3 phases. Fe and F atoms are represented by brown and blue spheres, respectively. In the case of FeF_3 -HTB, the different Fe and F positions are labeled and only one layer of atoms along the c-axis is shown in order to facilitate visualization.

Table 3. DFT calculated formation energies for OH^- substitution in the F^- sublattice of HTB and distorted ReO_3 -type FeF_3 (eV/formula unit).

Defect	Energy (eV/formula unit)
OH_{F1}	0.011
OH_{F2}	0.013
OH_{F3}	0.020
OH_{F4}	0.021
OH_{F} (ReO_3)	0.027

It is worth noting that within the HTB structure, the OH_{F1} and OH_{F2} substitutions were found to have the lowest formation energies compared to OH_{F3} and OH_{F4} , which indicates that the fluoride substitution by OH groups is favored within the hexagonal section of the network. A structural comparison between $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ and the HTB structure shows that the HTB F1 and F2 sites result from the condensation of the equatorial positions of FeF_6 and $\text{FeF}_2(\text{H}_2\text{O})_4$ octahedra from $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$. This implies that F1 and F2 sites are likely partially hydroxylated while F3 and F4 sites that derived from the axial fluoride sites in $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ are fluorinated sites.

4. CONCLUSIONS

The combination of experimental and computational tools employed in this study allowed a complete determination of the atomic structure of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$. Rietveld analysis of the powder x-ray diffraction pattern of this compound yielded an average description of the structure with a building unit consisting of $\text{FeF}_4(\text{H}_2\text{O})_2$ octahedra. However, DFT and Mössbauer spectroscopy pointed toward the existence of two distinct Fe^{3+} environments with FeF_6 and $\text{FeF}_2(\text{H}_2\text{O})_4$ octahedra yielding a structure built from infinite chains of $[\text{FeF}_6]_n$ and $[\text{Fe}_2(\text{H}_2\text{O})_4]_n$ held by hydrogen bonds.

Thermal analysis revealed that the decomposition of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ involves the inter-condensation of these chains of $[\text{FeF}_6]_n$ and $[\text{Fe}_2(\text{H}_2\text{O})_4]_n$ through hydrolysis and dehydration/olation reactions. Thus, the decomposition of chains of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ produces a mixed anionic compound whose structure is dictated by the decomposition conditions. The use of a self-generated atmosphere favors the stabilization of the hexagonal-tungsten-bronze type structure with OH groups being partially substituted for fluoride anions due to hydrolysis. This phase can be used as electrode for batteries.

ACKNOWLEDGEMENTS

The research leading to these results has received funding from the People Programme (Marie Curie Actions) of the European Union's Seventh Framework Programme (FP7/2007-2013) under REA grant agreement n°[321879] (FLUOSYNES). We also thank the Hydro-Québec Company and the University Pierre and Marie Curie for funding. The work done at the Advanced Photon Source, an Office of Science User Facility operated for the U.S. Department of Energy (DOE) Office of Science by Argonne National Laboratory, was supported by the U.S. DOE under Contract No. DE-AC02-06CH11357.

Supporting Information. Complementary data including structural data, TGA, SEM, and DFT calculations.

Corresponding Author

*damien.dambournet@upmc.fr

REFERENCES

- (1) Pereira, N.; Badway, F.; Wartelsky, M.; Gunn, S.; Amatucci, G. G. *J. Electrochem. Soc.* **2009**, *156*, A407–A416.
- (2) Larcher, D.; Tarascon, J.-M. *Nat. Chem.* **2015**, *7*, 19–29.
- (3) Forsberg, K. M.; Rasmuson, Å. C. *J. Cryst. Growth* **2006**, *296*, 213–220.
- (4) Forsberg, K. M.; Rasmuson, Å. C. *Miner. Eng.* **2007**, *20*, 950–955.
- (5) Sanghvi, S.; Pereira, N.; Halajko, A.; Amatucci, G. G. *RSC Adv* **2014**, *4*, 57098–57110.
- (6) Kim, S.-W.; Seo, D.-H.; Gwon, H.; Kim, J.; Kang, K. *Adv. Mater.* **2010**, *22*, 5260–5264.
- (7) Liu, L.; Guo, H.; Zhou, M.; Wei, Q.; Yang, Z.; Shu, H.; Yang, X.; Tan, J.; Yan, Z.; Wang, X. *J. Power Sources* **2013**, *238*, 501–515.
- (8) Dambournet, D.; Duttine, M.; Chapman, K. W.; Wattiaux, A.; Borkiewicz, O.; Chupas, P. J.; Demourgues, A.; Groult, H. *J. Phys. Chem. C* **2014**, *118*, 14039–14043.
- (9) Li, C.; Yin, C.; Mu, X.; Maier, J. *Chem. Mater.* **2013**, *25*, 962–969.
- (10) Leblanc, M.; Ferey, G.; Chevallier, P.; Calage, Y.; De Pape, R. *J. Solid State Chem. Fr.* **1983**, *47*, 53–58.
- (11) Duttine, M.; Dambournet, D.; Penin, N.; Carlier, D.; Bourgeois, L.; Wattiaux, A.; Chapman, K. W.; Chupas, P. J.; Groult, H.; Durand, E.; Demourgues, A. *Chem. Mater.* **2014**, *26*, 4190–4199.
- (12) Rodríguez-Carvajal, J. *Comm. POWDER Diffr. Newsl.* **2001**, *26*.
- (13) Brand, R. WinNormos software, Universität Duisburg-Essen: Duisburg, Germany, 2008.
- (14) Qiu, X.; Thompson, J. W.; Billinge, S. J. L. *J. Appl. Crystallogr.* **2004**, *37*, 678–678.
- (15) Farrow, C. L.; Juhas, P.; Liu, J. W.; Bryndin, D.; Božin, E. S.; Bloch, J.; Proffen, T.; Billinge, S. J. L. *J. Phys. Condens. Matter* **2007**, *19*, 335219.
- (16) Kresse, G.; Hafner, J. *Phys. Rev. B* **1994**, *49*, 14251–14269.
- (17) Kresse, G.; Furthmüller, J. *Phys. Rev. B* **1996**, *54*, 11169–11186.
- (18) Jain, A.; Ong, S. P.; Hautier, G.; Chen, W.; Richards, W. D.; Dacek, S.; Cholia, S.; Gunter, D.; Skinner, D.; Ceder, G.; Persson, K. a. *APL Mater.* **2013**, *1*, 011002.
- (19) Blöchl, P. E. *Phys. Rev. B* **1994**, *50*, 17953–17979.
- (20) Kresse, G.; Joubert, D. *Phys. Rev. B* **1999**, *59*, 1758–1775.
- (21) Murnaghan, F. D. *Proc. Natl. Acad. Sci. U. S. A.* **1944**, *30*, 244–247.
- (22) Chevrier, V. L.; Hautier, G.; Ong, S. P.; Doe, R. E.; Ceder, G. *Phys Rev B* **2013**, *87*, 094118.
- (23) Teufer, G. *Acta Crystallogr. 0365-110X* **1964**, *17*, 1480.

- (24) Chupas, P. J.; Corbin, D. R.; Rao, V. N. M.; Hanson, J. C.; Grey, C. P. *J. Phys. Chem. B* **2014**, *107*, 8327–8336.
- (25) Kemnitz, E.; Groß, U.; Rüdiger, S.; Scholz, G.; Heidemann, D.; Troyanov, S. I.; Morosov, I. V.; Lemée-Cailleau, M.-H. *Solid State Sci.* **2006**, *8*, 1443–1452.
- (26) Grau-Crespo, R.; Hamad, S.; Catlow, C. R. A.; Leeuw, N. H. de. *J. Phys. Condens. Matter* **2007**, *19*, 256201.
- (27) Feist, M.; Kemnitz, E. *Honour Issue Retire. Prof W Hemminger* **2006**, *446*, 84–90.
- (28) Menz, D. H. *J. Therm. Anal.* **1992**, *38*, 321–334.
- (29) Leblanc, M.; Pannetier, J.; Férey, G.; Pape, R. D. *Rev Chim Min.* **1985**, *22*, 107–114.

TOC: The structure of $\text{FeF}_3 \cdot 3\text{H}_2\text{O}$ was resolved using a combined experimental and computational approaches yielding a fine local description of the water and fluoride arrangements. The structural description was used to understand the decomposition path of the hydrate phase and further enabled to stabilize a hydroxyfluoride compound featuring the HTB type structure.

