



Effect of plasticity and atmospheric pressure on the formation of donut- and croissantlike buckles

S. Hamade, J. Durinck, G. Parry, C. Coupeau, A. Cimetière, Jean Grilhé,
Jérôme Colin

► To cite this version:

S. Hamade, J. Durinck, G. Parry, C. Coupeau, A. Cimetière, et al.. Effect of plasticity and atmospheric pressure on the formation of donut- and croissantlike buckles. *Physical Review E: Statistical, Nonlinear, and Soft Matter Physics*, 2015, 91 (1), 10.1103/PhysRevE.91.012410 . hal-01216770

HAL Id: hal-01216770

<https://hal.science/hal-01216770>

Submitted on 9 Apr 2024

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Effect of plasticity and atmospheric pressure on the formation of donut and croissant-like buckles

S. Hamade^{1,*}, J. Durinck¹, G. Parry², C. Coupeau¹, A. Cimetière¹, J. Grilhé¹, and J. Colin¹

¹ *Institut P', Université de Poitiers, ENSMA, SP2MI-Téléport 2,
86962 Futuroscope-Chasseneuil cedex, France. and*

² *Science et Ingénierie des Matériaux et Procédés, Université de Grenoble,
1130 rue de la Piscine, BP 75, 38402 St Martin d'Heres cedex, France.*

(Dated: November 21, 2014)

The formation of donut and croissant-like buckles has been observed onto the free surface of gold thin films deposited on silicon substrates. Numerical simulations clearly evidence that the coupling effect between the atmospheric pressure acting on the free surface and the plastic folding of the ductile film is responsible for the circular blister destabilization and the formation of the donut and croissant-like buckling patterns.

PACS numbers: 68.55.-a Thin film structure and morphology, 46.32.+x Static buckling and instability, 62.25.-g Mechanical properties of nanoscale systems.

The control of the mechanical properties of multilayered structures is a long standing problem that has been intensively studied from both experimental and theoretical point of view because of the numerous applications of such patterns in electronic and optoelectronic devices [1]. The delamination and buckling of thin films deposited on substrates have been for example investigated when the films are internally strained due to lattice and/or thermal expansion coefficient mismatches between the film and the substrate [2–4]. In the framework of the Föppl von Kármán (FvK) theory of thin plates [5, 6], different structures observed at the nano (and meso) scales with the help of atomic force (optical) microscope have been thus characterized such as circular blisters, straight-sided and telephone cord buckles. The critical stress beyond which the straight-sided blisters appear has been for example determined as well as the film profiles after buckling. Likewise, the effects of the substrate elasticity and stress anisotropy have been characterized and a stability diagram has been provided for the formation of the circular blisters, straight-sided and telephone cord buckles [7]. The effect of the thin film plasticity has been then considered and the formation of folded structures observed onto the surface of ductile gold thin films has been explained [8, 9]. Recently, the effect of overpressure between the upper and lower surfaces of the films has been investigated on the morphological evolution of buckles generated by internal strains. It has been found that this overpressure is responsible for the partial redeposition of the buckled part of the films [11]. An experimental study of the buckling of nickel thin films deposited on polycarbonate substrates has also evidenced a pressure mismatch between the outer free surface of the film and the inner film-substrate interface. The presence of vacuum has thus been deduced between the film and its substrate [12].

In this letter, the combined effects of internal stress, atmospheric pressure applied onto the film free surface and thin film plasticity have been investigated on the buckling patterns through finite element simulations. The formation of donut and croissant-like morphologies experimentally observed on the surface of a gold thin film has been explained in the framework of the continuum non-linear mechanics.

Gold films have been first deposited by sputtering methods on silicon wafers. The physical vapor deposition (PVD) technique leads to homogeneous films with well-defined constant thicknesses. The thickness of the Au films has been determined by DEKTAK mechanical profilometry to be equal to $h = 630 \text{ nm}$. It has been observed in Fig. 1a that after removing the specimens from the deposition chamber, the thin films exhibit a plethora of buckling structures among which one can cite the circular blisters, croissant-like and donut-like buckles. A correlation between the dimensions and the shapes of such structures has been then established in Fig. 1b. It can be observed that circular buckles develop for the smallest delamination area at the interface (region A) while croissant and donut-like shapes appear for the intermediate and largest areas corresponding to regions B and C, respectively. Two critical widths have thus been determined, $2b_c^1 \sim 71 \mu\text{m}$ and $2b_c^2 \sim 127 \mu\text{m}$ that characterize the blister to croissant-like buckle and the croissant to donut-like buckle transitions, respectively. It can be emphasized at this point that the transition from blister to croissant-like buckles is supposed to depend on buckle plastic deformation and the local stress state in the film. Since these parameters may vary in our experimental conditions for a given sample, a few of circular blisters and croissant-like buckles can be experimentally observed for similar widths. It can also be underlined that such large buckling structures (reaching sometimes $200 \mu\text{m}$ wide) are rarely mentioned in the literature, since the full delamination of the film-substrate interface usually occurs. Evidences of thin film plasticity are provided in Fig. 1c. Indeed, fine surface features are observed on

*Electronic address: sami.hamade@univ-poitiers.fr

the flat part of the croissant-like structures as well as a superposition of several circular buckles. These observations can be ascribed to plastic events already observed in similar systems at the circumference of buckles [8, 9] and support the idea of a complete initial circular delamination at the film-substrate interface before the partial redeposition takes place, leading to croissant or donut-like structures.

In order to describe the effect of pressure and plasticity on the post-buckling regime of a circular blister, a geometrically non-linear plate is used in order to model the thin film. The substrate surface is represented by a rigid plane forbidding the displacement of the plate in the lower half-space (unilateral contact condition) such that the elastic deformation of the substrate is not considered.

The plate is a circular domain Ω with center O and half width b and is originally flat with its midplane located at the substrate surface (see Fig. 2a). Let us denote (Oz) the direction of the normal to the substrate surface. For convenience, a cylindrical coordinate system of axis (Oz) is used to describe the kinematic of the plate, and $u(r, \theta)$, $v(r, \theta)$ and $w(r, \theta)$ are the displacement components along the axes parallel to \vec{e}_r , \vec{e}_θ and \vec{e}_z , respectively, for any point $M(r, \theta)$ of the midplane. The boundary conditions are imposed along the edge $\partial\Omega$ of the plate, $\partial\Omega = \{M(b, \theta), 0 \leq \theta < 2\pi\}$, such that:

$$\forall M \in \partial\Omega, u(M) = v(M) = w(M) = 0, \frac{\partial w}{\partial r}(M) = \beta, \quad (1)$$

where β is an angle defined in order to mimic the plastic folding. The various buckling patterns are characterized by large values of the out-of-plane displacement component $w(r, \theta)$ such that the calculations must be carried out within the framework of large displacement hypothesis using the Green Lagrange strain tensor. The plate is submitted to three loading steps:

- Step 1: application of the internal stress.

The parameter β is set to zero, yielding to the classical clamped edge conditions usually invoked for the buckling of elastic thin films on rigid substrates [2]. An internal compressive stress is introduced in the film as: $\sigma_{rr} = \sigma_{\theta\theta} = -E_f/(1 - \nu_f)\epsilon_0 = -\sigma_0$ and $\sigma_{r\theta} = 0$, with ϵ_0 a positive and constant eigenstrain, E_f and ν_f the Young's modulus and Poisson's ratio of the film, respectively. For a gold thin film, one will take in the following $E_f = 79$ GPa and $\nu_f = 0.44$. At this point, the obtained solution corresponds to the classical circular blister [2]. Note that the eigenstrain is maintained during the next steps.

- Step 2: mimicking the plastic folding.

In order to mimic the plastic folding at the buckle edge, a folding angle β has been imposed all along the circumference $\partial\Omega$ of the clamped buckle. This angle whose value will be specified later is maintained during the procedure. At this point, it can be underlined that the shape of the blisters remains circular, with a smooth change of geometry.

- Step 3: application of the pressure.

A uniform overpressure $\Delta p = p_e - p_i$ is applied, with p_e and p_i the pressures applied onto the upper and lower surfaces of the buckled film, respectively. The equilibrium can be dramatically modified by this loading, leading to secondary buckling equilibria quite remote from the original circular shape in the post-critical regime (see Fig. 2b).

In order to carry out these non-linear calculations, finite element simulations have been performed using the software ABAQUS [13]. An implicit scheme has been selected. Quadrilateral shell elements have been used to mesh the film. The element sizes have been chosen in such a way that a minimum of 28 elements are considered into the film along the diameter.

In the following, the results of the calculation have been rationalized using non-dimensional parameters for the loading. Hence, $\tilde{\sigma}_0$ and $\Delta\tilde{p}$ have been defined as:

$$\tilde{\sigma}_0 = \frac{12\sigma_0}{\tilde{E}_f} \frac{1}{\tilde{h}^2}, \Delta\tilde{p} = \frac{12\Delta p}{\tilde{E}_f} \frac{1}{\tilde{h}^4}, \quad (2)$$

with $\tilde{h} = h/b$, $\tilde{E}_f = E_f/(1 - \nu_f^2)$ and b the half-width of the delaminated interface. Before applying the loading steps 1 and 3, an initial modification of the out-of-plane displacement $\tilde{w} = w/h$ has been applied to a circular blister of width $2b$ and maximum out-of-plane displacement $10^{-4}b$ in order to facilitate the thin film evolution. For each stress state of the film $(\tilde{\sigma}_0, \beta, \Delta\tilde{p})$, five different perturbations of the initial displacement \tilde{w} of the circular blister, corresponding to the first five buckling modes of the film have been tested. The most stable equilibrium pattern is then determined for a given loading state $(\tilde{\sigma}_0, \beta, \Delta\tilde{p})$ which corresponds to the structure of minimum potential energy.

The buckling has been investigated considering first that no plasticity occurs in the film in order to focus on the pressure effect on buckling patterns. The calculations have been thus carried out ignoring the loading step 2 described above and keeping $\beta = 0$. A shape diagram for the buckles has been displayed in Fig. 3 in the $(\tilde{\sigma}_0, \Delta\tilde{p})$ plane, where the values of the out-of-plane displacement of the film \tilde{w} have been added on a color scale. It can be noticed that the dimensionless value of the overpressure $\Delta\tilde{p} = 2090$ would correspond to the application of the atmospheric pressure on the free surface of the considered gold thin film ($h = 630$ nm), the internal pressure between the film and the substrate being zero in the vacuum hypothesis [12]. It is clearly evidenced in Fig. 3 that the coupled effect of $\Delta\tilde{p}$ and $\tilde{\sigma}_0$ is to destabilize the circular blisters and to facilitate, as it increases, the formation of a plethora of buckle morphologies such as croissant-like, two and three lobe structures. However, it appears that the donut-like morphology observed onto the surface of the gold thin film does not emerge from this first numerical analysis. The next step of this present paper has been thus to consider the effect of plasticity of

the ductile thin film. To do so, it is assumed that, following previous experimental studies [9], the plasticity of the ductile film results in the formation of a plastic folding characterized by an angle taken to be constant all along the circumference of the buckle, $\beta = 5^\circ$ (See Supplemental Material at [14]). A new shape diagram has been thus constructed in the $(\tilde{\sigma}_0, \Delta\tilde{p})$ plane using the same procedure as the one already described in the plasticity free case. This new diagram taking into account the thin film folding is presented in Fig. 4. It can be observed in this Fig. 4 that the main effect of folding is to stabilize the buckle circumference in such a way that only two shapes promoted by the overpressure appear to be selected: the donut and croissant-like morphologies. Indeed, when $\tilde{\sigma}_0$ is high and $\Delta\tilde{p}$ is small, the circular blister pattern is expected, otherwise the donut and croissant-like patterns dominate. The boundary characterizing the transition between these two regimes of buckles has been superimposed in Fig. 4 (see the full dark line).

In order to characterize the influence of the atmospheric pressure on buckling, the previous results obtained by means of finite element simulations have been analyzed in the case of the gold thin films deposited on silicon substrates firstly presented that are lying in the air condition. An internal compressive stress $\sigma_0 = 321$ MPa and a folding angle $\beta = 5^\circ$ have been considered (See Supplemental Material at [14]). Taking an overpressure $\Delta p = 0.1$ MPa (or $\Delta\tilde{p} = 2090$) corresponding to the atmospheric overpressure, it can be observed in Fig. 5 that the different buckle morphologies observed at different delamination widths $2b$ on the surface of the gold thin film, i.e. a circular blister for $2b = 50\mu\text{m}$, a croissant-like buckle for $2b = 118\mu\text{m}$ and a donut-like buckle for $2b = 144\mu\text{m}$, have been also obtained in our simulations considering the overpressure and thin film plasticity.

Finally, the buckles corresponding to the minimum energy have been determined in Fig. 6 as a function of the delamination width $2b$, in the case where an overpres-

sure of the order of the atmospheric pressure is acting on the surface of the film, with an internal bi-axial stress $\sigma_0 = 321$ MPa and a folding angle $\beta = 5^\circ$. Three separated regions labeled A, B and C have been thus identified in Fig. 6b in good agreement with the statistical diagram derived from the experimental observations presented in Fig. 6a. In particular, the two critical widths $2b_c^1 \sim 104\mu\text{m}$ and $2b_c^2 \sim 134\mu\text{m}$ characterizing the blister to croissant-like buckle and the croissant to donut-like buckle transitions derived from the simulations are of the good order of magnitude with the experimental ones. It can also be underlined that the residual plasticity traces experimentally observed in Fig. 1b have been obtained in the simulations of the croissant-like buckles for $b \in [b_c^1, b_c^2]$, where the vertical deformation located near the circumference of the former circular blisters are still present.

In this Letter, the coupled effects of pressure and thin film plasticity have been characterized on the buckling patterns appearing onto the surface of thin films deposited on substrates and a shape diagram has been derived for the buckles by means of finite element simulations. It is clearly evidenced that an overpressure of the order of the atmospheric pressure and a plastic folding along the circumference of the buckles can explain the formation of the donut and croissant-like buckles observed for different widths of interface delamination in the case of ductile gold thin films. It is believed that a dynamic study of the evolution of the buckling structure under pressure and compression stress should be now performed considering the interaction between the delamination process and buckling phenomenon in order to get a more complete overview of the thin film ageing.

Acknowledgments: This work pertains to the French Government program Investissements d’Avenir (LABEX INTERACTIFS, reference ANR-11- LABX-0017-01).

-
- [1] L.B. Freund, and S. Suresh, *Thin Film Materials: Stress, Defect Formation and Surface Evolution*, Cambridge University Press. 355-366 (2003).
 - [2] J.W. Hutchinson, and Z. Suo, *Adv. Appl. Mech.* **29**, 63-191 (1992).
 - [3] M.W. Moon, H.M. Jensen, J.W. Hutchinson, K.H. Oh, and A.G. Evans, *J. Mech. Phys. Solids* **50**, 2355-2377 (2002).
 - [4] B. Audoly, *Phys. Rev. Lett.* **83**, 4124-4127 (1999).
 - [5] A. Foppl, *Vorlesungen uber Technishe Mechanik*, Springer, Wien **5**, 132 (1907).
 - [6] T.V. Kármán, *Encyklopadie der Mathematischen Wissenschaften*, B. G. Teubner, Leipzig **IV/4C**, 311-385 (1910).
 - [7] G. Parry, A. Cimetière, C. Coupeau, J. Colin, and J. Grilhé, *Phys. Rev. E* **74**, 066601 (2006).
 - [8] F. Foucher, C. Coupeau, J. Colin, A. Cimetière, and J. Grilhé, *Phys. Rev. Lett.* **97**, 096101 (2006).
 - [9] J. Colin, C. Coupeau, and J. Grilhé, *Phys. Rev. Lett.* **99**, 046101 (2007).
 - [10] E. Dion, J. Grilhé, J. Colin, and C. Coupeau, *J. Appl. Mech.* **77**, 041012 (2010).
 - [11] J. Colin, C. Coupeau, J. Durinck, A. Cimetière, and J. Grilhé, *Phys. Rev. E* **89**, 032410 (2014).
 - [12] C. Coupeau, J. Grilhé, E. Dion, L. Dantes de Moraes, and J. Colin, *Thin Solid Films* **518**, 5233 (2010).
 - [13] ABAQUS. ABAQUS analysis users manual, version 6.12 (2012).
 - [14] See supplemental materials at [] for the justification of stress and folding angle values from three dimensional finite element simulations with a power law work hardening model.

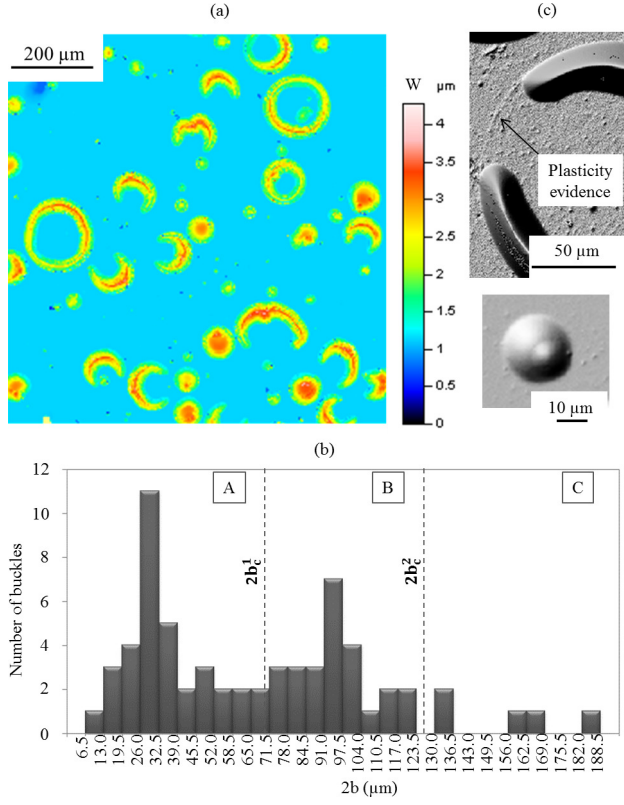


FIG. 1: Optical observations of the surface of a gold thin film of thickness $h = 630 \text{ nm}$ after its deposition on a silicon substrate. (a) Panoramic view of the surface. (b) Statistical description of the different morphologies of buckles as a function of diameter $2b$. Three regions A, B and C have been identified where circular blisters, croissant-like and donut-like buckles develop, respectively. (c) Experimental evidences of thin film plasticity: fine surface features on the flat part of a croissant-like structure and buckle superposition with plastic folding at the buckle circumferences.

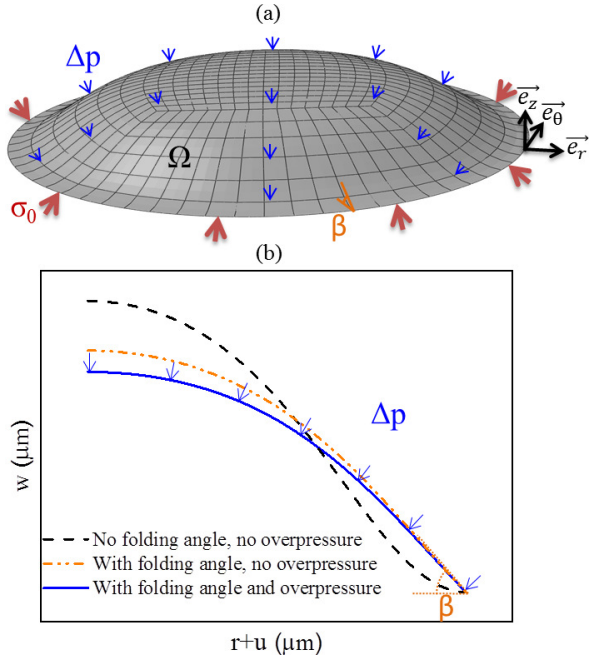


FIG. 2: (color online). (a) Schematic representation of the meshed circular buckle with a folding angle β used in the FEM simulations. A radial compression stress σ_0 and an external overpressure Δp are applied to the structure. (b) Sketch of the effect of the overpressure and plastic folding angle onto the buckle morphology.

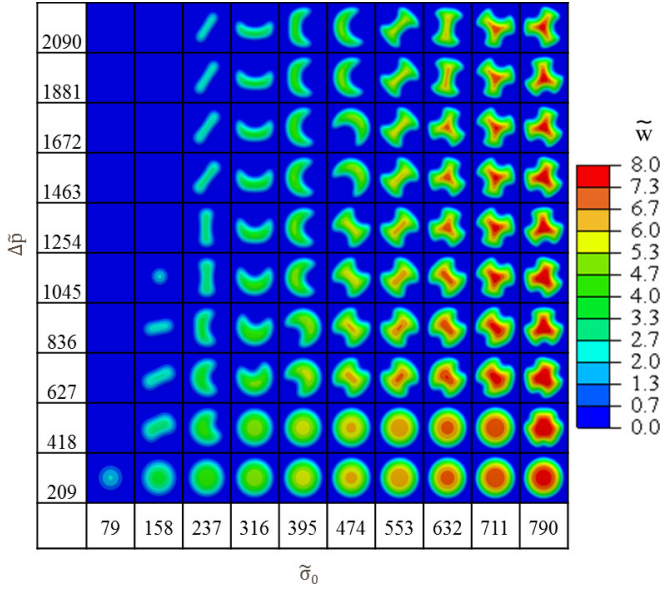


FIG. 3: (color online). Shape diagram in the $(\tilde{\sigma}_0, \Delta \tilde{p})$ plane for the buckle without any plasticity, i.e. for $\beta = 0^\circ$. The color scale for the normalized out-of-plane displacement \tilde{w} of the film is also displayed.

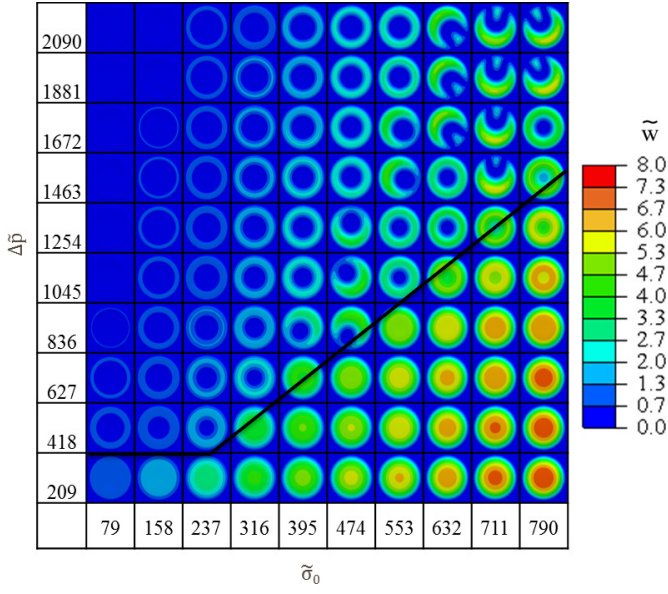


FIG. 4: (color online). Shape diagram in the $(\tilde{\sigma}_0, \Delta \tilde{p})$ plane for the buckles undergoing plastic folding characterized by a folding angle $\beta = 5^\circ$. The values of the out-of-plane displacement are presented on the color scale. The full black line corresponds to the boundary between the regime of formation of circular blisters and the regime of formation of donut and croissant-like buckles

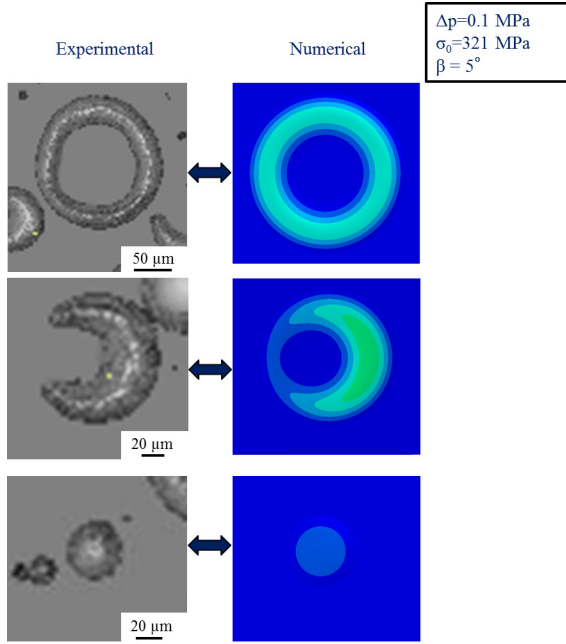


FIG. 5: Comparison between three experimental and numerical shapes of the buckles for an atmospheric overpressure $\Delta p = 0.1 \text{ MPa}$, an internal radial compression stress $\sigma_0 = 321 \text{ MPa}$ and a folding angle $\beta = 5^\circ$.

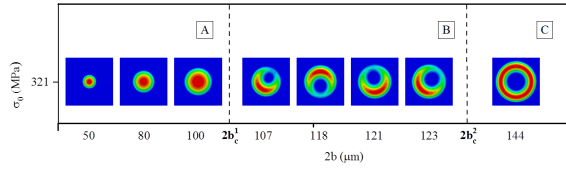


FIG. 6: Buckle patterns as a function of the delamination width $2b$. Finite elements results for a fixed atmospheric pressure $\Delta p = 0.1$ MPa, an internal compression stress $\sigma_0 = 321$ MPa and a folding angle $\beta = 5^\circ$.