



**HAL**  
open science

## Brilliant glyconanocapsules for trapping of bacteria

Xibo Yan, Adeline Sivignon, Pierre Alcouffe, Béatrice Burdin, Sabine Favre-Bonte, Rostyslav Bilyy, Nicolas Barnich, Etienne Fleury, Francois Ganachaud, Julien Bernard

► **To cite this version:**

Xibo Yan, Adeline Sivignon, Pierre Alcouffe, Béatrice Burdin, Sabine Favre-Bonte, et al.. Brilliant glyconanocapsules for trapping of bacteria. *Chemical Communications*, 2015, 51 (67), pp.13193-13196. 10.1039/c5cc04653j . hal-01221578

**HAL Id: hal-01221578**

**<https://hal.science/hal-01221578v1>**

Submitted on 17 Dec 2024

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

## Brilliant Glyconanocapsules for Trapping of Bacteria

Xibo Yan,<sup>a</sup> Adeline Sivignon,<sup>b,c</sup> Pierre Alcouffe,<sup>a</sup> Béatrice Burdin,<sup>d</sup> Sabine Favre-Bonté,<sup>e</sup> Rostyslav Bilyy,<sup>f</sup> Nicolas Barnich,<sup>b,c</sup> Etienne Fleury,<sup>a</sup> François Ganachaud<sup>a</sup> and Julien Bernard<sup>a,\*</sup>

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

**Nanoprecipitation of miglyol into droplets surrounded by a functional glycopolymer generates nanocapsules of biointerest. Fluorophores are trapped in situ or post-grafted onto the crosslinked polymer shell for efficient imaging. The resulting colloids induce aggregation of bacteria through strong specific interactions and promote bacterial removal.**

Sugar moieties play a prominent role in a myriad of biological processes, which explains the latest development of glycomimetics to simulate the attributes of naturally occurring oligo- or polysaccharides.<sup>1</sup> Monosaccharides generally weakly interact with their receptors, whereas several epitopes grafted on a common scaffold (multivalent molecules, dendrimers, polymer chains) show enhanced activities - thanks to the cluster glycoside effect - for targeting specific glycan-binding proteins.<sup>2</sup> Owing to their dimensions and multivalent ligand presentation, so-called glyconanomaterials constitute a remarkable platform for applications in imaging, biosensors, targeted drug delivery, enzyme inhibition and so on.<sup>3</sup> These include metal particles, fullerenes, nanodiamonds, (carbon) nanotubes or polymer nano-assemblies such as micelles, particles or capsules decorated with carbohydrates.<sup>3</sup> In spite of their significance in biological and medical fields, glyconanocapsules remain far less developed, surely because of their tricky preparation. Most examples of glyconanocapsule syntheses reported in the literature lately rely on block copolymers self-assembly,<sup>4</sup> LbL deposition of glycopolymers on a sacrificial template,<sup>5</sup> or interfacial polymerization.<sup>6</sup> Recently, we demonstrated that a careful

establishment and reading of both oil and polymer phase diagrams allows for setting conditions ensuring the rapid preparation of nanocapsules in a simple batch mixing.<sup>7</sup> This concomitant nanoprecipitation/polymer crosslinking procedure (called "Shift'N'Go process") also permits the simultaneous functionalization of the shell and filling of the core with molecules of biological interest.

In this communication, we substantiate this proof of concept by preparing biocompatible functional capsules of utility for bio-applications. Particularly, we report on the one-pot synthesis of precisely defined, miglyol-filled, epoxide-functionalized glyconanocapsules and on subsequent post-modifications of the polymer shell via ring opening reactions. We show that the nanocapsules can be easily loaded with actives and that the presence of numerous pendent epoxides within the walls permits an efficient incorporation of relevant molecules such as ligands, probes or metal nanoparticles. Furthermore, the multiple *n*-heptyl  $\alpha$ -D-mannose motifs present at the capsule surface strongly interact with the lectin sugar-binding sites (adhesin FimH) of adhesive proteinaceous hair-like organelles (type 1 fimbriae) expressed by *Escherichia coli* (*E. coli*) to promote adhesion and infection of tissues.<sup>8</sup> The construction of tag-labelled nanocapsules, with bright fluorophores and/or coated magnetic nanoparticles, is exploited here to monitor aggregation kinetics between the mannosylated nano-objects and Adherent-Invasive *E. coli* bacteria (AIEC) and promote bacterial removal.

A water-soluble random copolymer of N-[7-( $\alpha$ -D-mannopyranosyloxy)heptyl] methacrylamide (HMM) and glycidyl methacrylate (GMA) was prepared by 4-cyano-4-(phenylcarbonothioylthio) pentanoic acid-mediated RAFT polymerization (P(HMM<sub>206</sub>-stat-GMA<sub>17</sub>),  $M_n$  NMR = 77.1 kg·mol<sup>-1</sup>,  $\bar{D}$  = 1.10, details in ESI). In order to account for the disparity between the relative reactivity ratios of the two monomers ( $r_{\text{GMA}} = 2.82/2.77$  and  $r_{\text{HMM}} = 0.14/0.13$  using Jaacks and Kelen-Tüdös methods, respectively, see Fig. S1) and the hydrophobicity of GMA, polymerizations were carried out in a semi-batch process using a low molar fraction of GMA (see experimental part in ESI for polymerization details).<sup>9</sup> This procedure maintains an homogeneous distribution of epoxide

<sup>a</sup> Université de Lyon, Lyon, F-69003, France ; INSA-Lyon, IMP, Villeurbanne, F-69621, France; CNRS, UMR 5223, Ingénierie des Matériaux Polymères, Villeurbanne, F-69621, France. Email: julien.bernard@insa-lyon.fr

<sup>b</sup> Clermont Université, UMR 1071, Inserm/Université d'Auvergne, 63000 Clermont-Ferrand, France.

<sup>c</sup> INRA, Unité Sous Contrat 2018, 63000, Clermont-Ferrand, France.


<sup>d</sup> Centre Technologique des Microstructures (CTμ), Université Claude Bernard Lyon 1, France.

<sup>e</sup> Université de Lyon, France Research Group on "Bacterial Opportunistic Pathogens and Environment". UMR 5557 Ecologie Microbienne, CNRS, Vetagro Sup and Université Lyon1, France.

<sup>f</sup> Friedrich-Alexander University of Erlangen-Nürnberg, Department of Internal Medicine 3-Rheumatology and Immunology, D-91054 Erlangen, Germany.

Electronic Supplementary Information (ESI) available. See

DOI: 10.1039/x0xx00000x

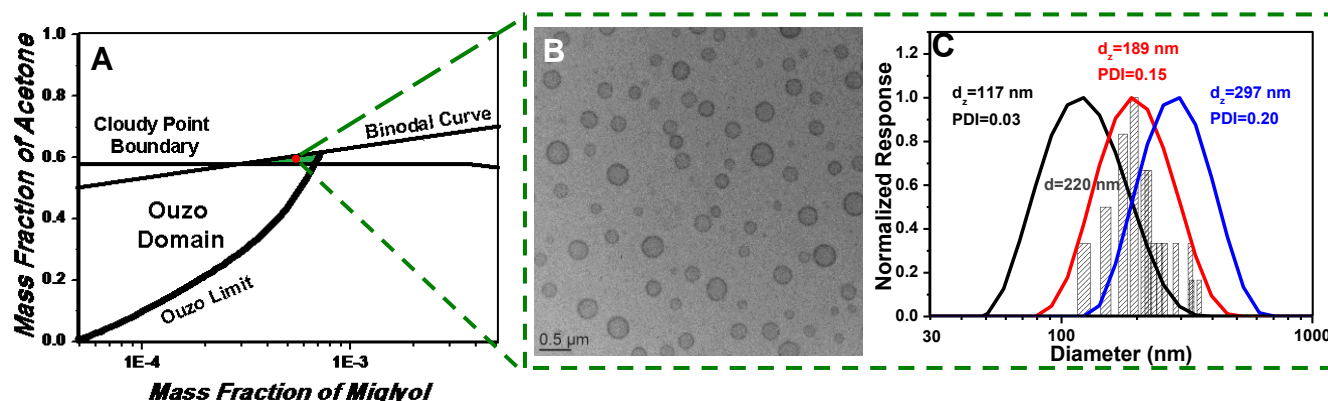

**Figure 1:** (A) Overlapped phase diagrams of P(HMM<sub>206</sub>-stat-GMA<sub>17</sub>) and miglyol in acetone/water mixtures. The domain in which nanocapsules can be generated through co-nanoprecipitation of miglyol and glycopolymer corresponds to the green zone of Fig 1A. Accordingly, nanoprecipitations were performed in the following conditions: polymer content = 0.025 wt %, miglyol content = 0.05 wt %, acetone content = 59 wt %. (B) TEM picture of the resulting glyconanocapsules (C) Comparison of DLS (from left to right, analyses performed in the conditions given in (A), Dulbecco's PBS buffer and distilled water) and TEM size distribution (histogram).

groups along the glycopolymer chains and thus avoids the formation of blocky, amphiphilic polymer chains prone to aggregate in water.


Glycopolymer and miglyol phase diagrams were subsequently established in water/acetone mixtures as described in our previous work (Fig. S3).<sup>7</sup> Polymer/oil/water/acetone compositions affording the simple one-pot preparation of glyconanocapsules via nanoprecipitation are easily identified by overlapping the two diagrams. Typically here, miglyol-filled glyconanocapsules are obtained for mass fractions of acetone and miglyol adjusted to 58–62 wt % and 0.05 wt %, respectively (see Figure 1A, green zone). This way, nanocapsules are repeatedly obtained in a simple batch mixing and in the full volume, provided that the solvent shifting procedure is carried out in the correct domain of composition.<sup>10</sup>

Besides, to circumvent potential destruction of the resulting nano-objects in water due to the desorption of the hydrophilic glycopolymer chains when removing the solvent, the walls of the capsules must be cross-linked (see Figs S4–S7). Isophorone diisocyanate (IPDI), a low water-sensitive difunctional linker, was used to “freeze” the structure of the nanocapsules by isocyanate/alcohol reaction. Robust spherical nanocapsules were fabricated in a reproducible manner using 48 eq of IPDI per chain (incorporated in the initial organic solution).<sup>11</sup> Miglyol was proven to remain sequestered in the inner part of the nanocapsules (see Fig. 1B). TEM pictures confirm the formation of nanocapsules with a diameter of around 220 nm in the dry state. Depending on the nature of the dispersion medium (nanoprecipitation conditions, PBS buffer or distilled water), particle size and particle size distribution observed by DLS measurement significantly differ (z-average diameter ranging from 117 nm in acetone/water mixture to 297 nm in distilled water and PDI from 0.02 to 0.20, see Fig 1C) reflecting the inclination of the nanocapsules membranes to substantially swell in favorable conditions. Importantly the glyconanocapsules exhibit good colloidal stability under such conditions and no aggregation is observed.

These *n*-heptyl  $\alpha$ -D-mannose-functionalized nanocapsules (HM-GC) are intended for bioapplications. In this view, the

capsules can be loaded with bioactive components in a one-pot procedure (see Figs. 2, S8 and S9). For instance, a fluoroquinolone antibiotic agent, Flumequine, was encapsulated in glyconanocapsules through dissolution in acetone prior to the nanoprecipitation (Figs. 2B and S9). Pyrene was also successfully encapsulated using this methodology (Fig. S8). All loadings were assessed by the fluorescence emission spectra of the dispersions after dialysis. The presence of a broad peak at 350–550 nm, depending on the fluorophore, confirmed the effectiveness of encapsulation. The pendent epoxides of the nanocapsules can be used as handles for post-nanoprecipitation attachment of molecules of interest (see Fig 2A). Owing to the broad applications of the biotin/streptavidine system in biotechnology, we biotinylated the membrane of the capsules with biotin ethylenediamine (1 eq per chain, 12h at 40°C, water). The decoration of the membrane has barely any impact on the dimensions of the nano-objects ( $D_z = 111$  nm, PDI = 0.3, Fig. S10); still, the presence of biotin motifs within the shell of the capsules was confirmed by the formation of large aggregates ( $\sim 600$ – $700$  nm) upon addition of tetrameric avidin and the capability of the glyco-nanocapsules to disrupt pre-established 4'-hydroxy-azobenzene 2-carboxylic acid/avidin complexes.

The glycopolymer membrane can also be functionalized with e.g. fluorescent tags and/or metal nanoparticles. To prove so, Alexa Fluor 555 Cadaverine (AFC) was added to a dispersion of nanocapsules and reacted overnight (1 eq of AFC per chain, 40°C). After functionalization, AFC-labelled HM-GC having a z-average diameter of 123 nm PDI=0.27) and displaying a typical fluorescence emission at 566 nm were obtained (Figs 2C and S11). Likewise, magnetic nanocapsules ( $D_z=126$  nm, Figs. 2D and S12) were prepared through post-nanoprecipitation modification with amino-functionalized carbon-coated cobalt magnetic nanoparticles (Co-NP,  $d \approx 30$  nm). Thanks to the covalent anchorage of Co-NP on their membranes, glyconanocapsules were rapidly and effectively recovered from the aqueous solution in the presence of a simple magnet (Figure 2D). Finally, we present below an example of biological assay made possible by these newly developed glyconanocapsules. First, we checked that after purification via

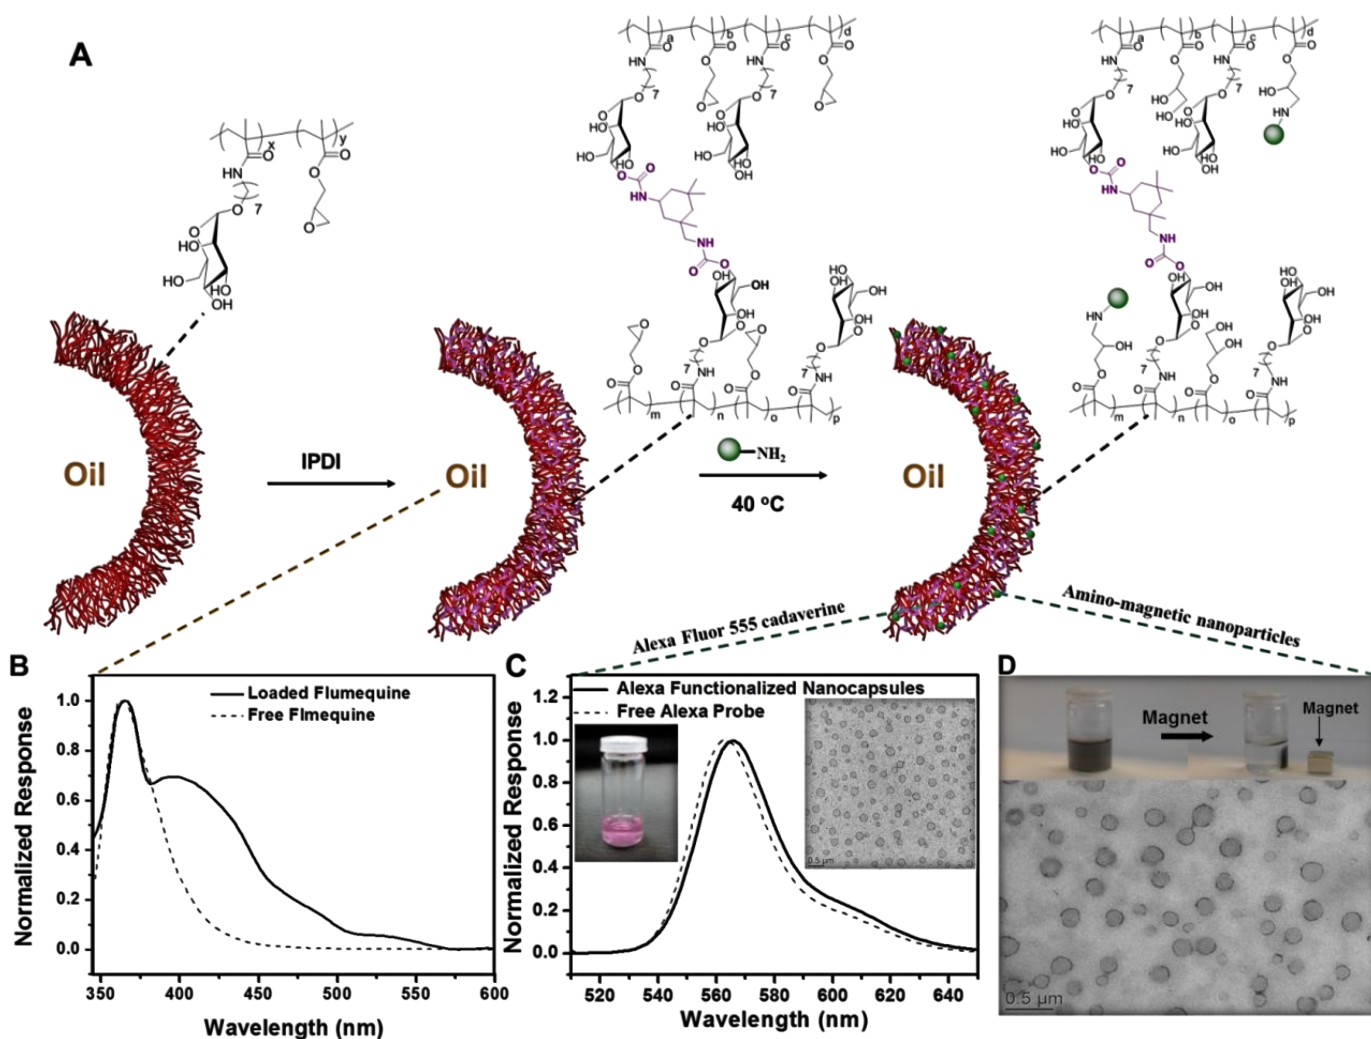

**Figure 2:** (A) Route to functional oil-filled glyconanocapsules through epoxy-amine post-nanoprecipitation modifications. (B) Fluorescence emission spectra of an aqueous solution of flumequine and of flumequine-loaded glyconanocapsules dispersion. (C) Fluorescence emission spectrum of AFC-functionalized glyconanocapsules; inset (top right corner): TEM picture of AFC-functionalized glyconanocapsules (scale bar: 0.5 μm), (top left corner) picture of AFC-functionalized glyconanocapsules. (D) TEM picture of CoNP-grafted glyconanocapsules (bottom) and their magnetically-driven separation from the aqueous solution (top).


dialysis, the epoxy- (functionalized glyconanocapsules are non-toxic (see tests in Fig. SXX). Given the remarkable affinity of *n*-heptyl  $\alpha$ -D-mannose for FimH adhesin (binding affinity of 5 nM recorded by SPR) exposed at the extremity of AIEC type 1 fimbriae,<sup>8</sup> the capability of HM-GC to interact with AIEC LF82 strains was then explored. In the absence of HM-GC, no cluster of green fluorescent AIEC LF82 ( $OD_{620nm} = 0.6$ , fluorescence emission at  $\sim 520$  nm) is observed after 3h suggesting that bacteria alone exhibit a poor tendency to self-aggregate under the conditions of analysis (see Supporting Information). Meanwhile, clusters of bacteria are observed when bacteria are incubated with glyconanocapsules in aqueous solution (Figs 3B-D). The glyconanocapsules efficiently agglutinate *E. coli* thanks to the strong interaction of pendent heptyl mannosides ligated to the membrane and FimH adhesins expressed at the surface of bacteria. Interestingly, the size of bacteria clusters increases with time of incubation (up to 40 μm after 3 h). The propensity of HM-GC to strongly interact with AIEC bacteria was further corroborated by bacterial adhesion assays. Infection of T84 cells with AIEC *E. coli*. previously incubated with HM-GC at 6 μg/mL of HM-GC resulted in extremely low level of

bacterial adhesion to T84 cells ( $\sim 5\%$  of residual adhesion, 100% corresponding to adhesion in absence of any compound see ESI).

To assess the specificity of the binding between HM-GC and AIEC LF82, the bacteria were also exposed to nanocapsules built from D-glucose containing glycopolymers (experimental details given in ESI). No cluster of bacteria was observed under such conditions (see Fig SXX).

HM-GC decorated with AFC allow for visualizing their interactions with *E. coli*. Red emitting glyconanocapsules gradually accumulate at the surface of the bacteria with time to promote interconnections between bacteria and ultimately agglutination. Both AFC and GFP tags produce images of sufficient quality to be overlapped (Fig. 3E, 3F and S14). AIEC LF82 strains ( $OD_{620nm} = 0.6$ ) were finally incubated at room temperature for 3h (after 3h, [AIEC LF82] =  $2 \times 10^7 \text{ mL}^{-1}$ ) with magneto-responsive HM-GC (0.5 mg in 100 μL) and a magnet was placed close to the suspension to promote the separation of the magneto-responsive materials from the solution (Fig. 2D).<sup>12</sup> Under such conditions, the nanocapsules achieved high yields of bacteria removal (83%, see details in ESI).



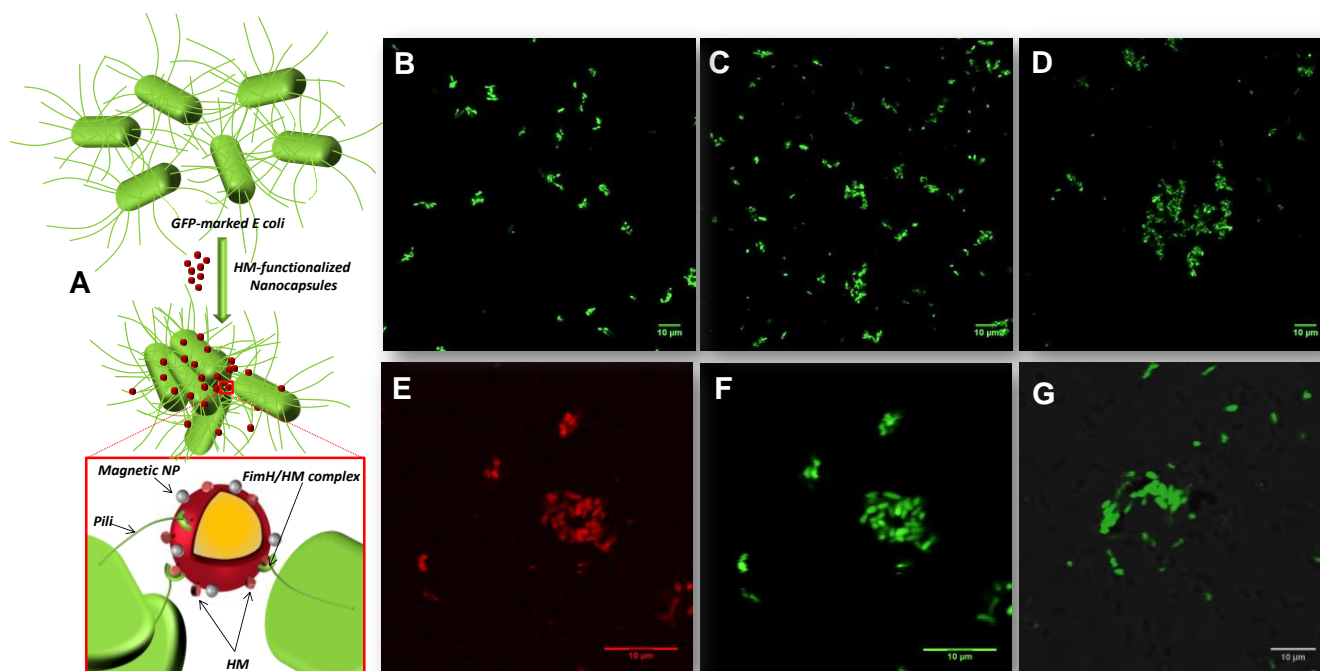

**Figure 3:** Left: A) Principle of bacterial agglutination in the presence of glyconanocapsules. Right: Up): Confocal fluorescence microscopy (CFM) pictures of GFP-marked AIEC LF82 incubated with HM-GC (66  $\mu\text{M}$ ) for 30 min (B), 2 h (C) and 3 h (D). Bottom: (E and F) CFM pictures of GFP-marked AIEC LF82 incubated for 2 h with AFC-functionalized capsules (66  $\mu\text{M}$ ) ( $\lambda_{\text{exc}} = 488 \text{ nm}$  for GFP and 543 nm for AFC). (G) CFM picture of GFP-marked AIEC LF82 clusters extracted from the solution by magnetically-driven separation.

Characterization of these aggregates by confocal fluorescence microscopy (after re-dispersion in water) confirmed the formation of stable glyconanocapsules/bacteria clusters that can be conveniently extracted from the aqueous solution, thanks to the cobalt nanoparticles within the walls of the nanocapsules (Figure 3G).

In conclusion, we have demonstrated that oil-filled, shell-functionalized glyconanocapsules can be reproducibly built and loaded with actives in a simple one-pot procedure. Epoxide-functionalized nanocapsules constitute a convenient platform for post-attachment of biologically relevant molecules or CoNP through epoxide-amine ring opening reactions. Thanks to the concomitant presence of numerous mannose residues and fluorophores or CoNP, kinetics of *E. coli* agglutination in the presence of the nanocapsules can be conveniently monitored and the resulting bacterial clusters efficiently extracted from solution via magnetically-driven separation.

## Notes and references

- 1 R. A. Dwek, *Chem. Rev.*, 1996, **96**, 683.
- 2 J. J. Lundquist and E. J. Toone, *Chem. Rev.*, 2002, **102**, 555.
- 3 a) N. C. Reichardt, M. Martin-Lomas and S. Penades, *Chem. Soc. Rev.*, 2013, **42**, 4358; b) R. Sunasee and R. Narain, *Macromol. Biosci.*, 2013, **13**, 9; c) X. Li and G. Chen, *Polym. Chem.*, 2015, **6**, 1417.
- 4 J. Huang, C. Bonduelle, J. Thevenot, S. Lecommandoux and A. Heise, *J. Am. Chem. Soc.*, 2012, **134**, 119.
- 5 H. L. Guo, Q. Q. Guo, T. C. Chu, X. G. Zhang, Z. M. Wu and D. M. Yu, *J. Mater. Sci.-Mater. M.*, 2014, **25**, 121.
- 6 a) R. Roux, L. Sallet, P. Alcouffe, S. Chambert, N. Sinteszdydowicz, E. Fleury and J. Bernard, *ACS Macro Lett.*, 2012, **1**, 1074; b) K. Malzahn, F. Marsico, K. Koynov, K. Landfester, C. K. Weiss and F. R. Wurm, *ACS Macro Lett.*, 2014, **3**, 40.
- 7 X. Yan, M. Delgado, A. Fu, P. Alcouffe, S. G. Gouin, E. Fleury, J. L. Katz, F. Ganachaud and J. Bernard, *Angew. Chem. Int. Ed.*, 2014, **53**, 6910.
- 8 a) J. Bouckaert, J. Berglund, M. Schembri, E. De Genst, L. Cools, M. Wuhler, C. S. Hung, J. Pinkner, R. Slattegard, A. Zavalov, D. Choudhury, S. Langermann, S. J. Hultgren, L. Wyns, P. Klemm, S. Oscarson, S. D. Knight and H. De Greve, *Mol. Microbiol.*, 2005, **55**, 441. b) X. Yan, A. Sivignon, N. Yamakawa, A. Crepet, C. Travelet, R. Borsali, T. Dumych, Z. Li, R. Bilyy, D. Deniaud, E. Fleury, N. Barnich, A. Darfeuille-Michaud, S. G. Gouin, J. Bouckaert and J. Bernard *Biomacromolecules*, 2015, DOI:10.1021/acs.biomac.5b00413
- 9 P. Escala, S. R. S. Ting, A. Khoukh, L. Rubatat, M. Save, M. H. Stenzel and L. Billon, *Macromolecules*, 2011, **44**, 5911.
- 10 Choosing HD as oil, the domain for the formation of nanocapsules is much larger. Then, the final content of acetone ranges from 58 to 70 wt% and the final weight fraction of HD  $\sim 0.05$  wt% (Figs. S6 and S7).
- 11 We also tried to crosslink the capsule walls by epoxy-amine reaction using cystamine to confer a degradable character to the capsules upon reduction of the S-S bond. Unfortunately, cross-linking procedures showed deficient reproducibility so far (see Fig S4).
- 12 a) D. M. Hatch, A. A. Weiss, R. R. Kale, S. S. Iyer *ChemBioChem* 2008, **9**, 2433. b) M. Bera, N. Azzouz, S. Schmidt, D. V. Volodkin, S. Mosca, M. Chanana, P. H. Seeberger, L. Hartmann *Biomacromolecules*, 2013, **14**, 1927.