



**HAL**  
open science

## Thermodynamic stability and kinetic inertness of a Gd–DTPA bisamide complex grafted onto gold nanoparticles

Vijetha Mogilireddy, Isabelle Déchamps-Olivier, Christophe Alric, Gautier Laurent, Sophie Laurent, Luce Vander Elst, Robert Müller, Rana Bazzi, Stéphane Roux, Olivier Tillement, et al.

### ► To cite this version:

Vijetha Mogilireddy, Isabelle Déchamps-Olivier, Christophe Alric, Gautier Laurent, Sophie Laurent, et al.. Thermodynamic stability and kinetic inertness of a Gd–DTPA bisamide complex grafted onto gold nanoparticles. *Contrast Media and Molecular Imaging*, 2015, 10 (3), pp.179-187. 10.1002/cmmi.1616 . hal-01275116

**HAL Id: hal-01275116**

**<https://hal.science/hal-01275116>**

Submitted on 12 Feb 2021

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Thermodynamic stability and kinetic inertness of a Gd–DTPA bisamide complex grafted onto gold nanoparticles

Vijetha Mogilireddy<sup>a</sup>, Isabelle Déchamps-Olivier<sup>a</sup>, Christophe Alric<sup>b</sup>, Gautier Laurent<sup>c</sup>, Sophie Laurent<sup>d</sup>, Luce Vander Elst<sup>d,e</sup>, Robert Muller<sup>d,e</sup>, Rana Bazzi<sup>c</sup>, Stéphane Roux<sup>c</sup>, Olivier Tillement<sup>b</sup> and Françoise Chuburu<sup>a\*</sup>



Gold nanoparticles coated by gadolinium (III) chelates (Au@DTDTPA) where DTDTPA is a dithiolated bisamide derivative of diethylenetriamine-*N,N,N',N'',N''*-pentaacetic acid (DTPA), constituted contrast agents for both X-ray computed tomography and magnetic resonance imaging. In an MRI context, highly stable Gd<sup>3+</sup> complexes are needed for *in vivo* applications. Thus, knowledge of the thermodynamic stability and kinetic inertness of these chelates, when grafted onto gold nanoparticles, is crucial since bisamide DTPA chelates are usually less suited for Gd<sup>3+</sup> coordination than DTPA. Therefore, these parameters were evaluated by means of potentiometric titrations and relaxivity measurements. The results showed that, when the chelates were grafted onto the nanoparticle, not only their thermodynamic stability but also their kinetic inertness were improved. These positive effects were correlated to the chelate packing at the nanoparticle surface that stabilized the corresponding Gd<sup>3+</sup> complexes and greatly enhanced their kinetic inertness. Copyright © 2014 John Wiley & Sons, Ltd.

Additional supporting information may be found in the online version of this article at the publisher's web site.

**Keywords:** imaging agents; gadolinium chelates; nanoparticles; thermodynamics; kinetics

## 1. INTRODUCTION

Since its beginning in medical imaging, magnetic resonance imaging (MRI) has become an irreplaceable tool in diagnostic medicine. The reason of its success is based on the images obtained with excellent soft tissue contrast that allow anatomy assessment with an excellent spatial resolution. This noninvasive technique can also provide information on the physicochemical state of tissues, their vascularization and their function (1,2). MRI relies on the longitudinal ( $T_1$ ) and transverse ( $T_2$ ) proton relaxation times of mainly water. The intrinsic relaxation times of tissue water are dependent on the physiological environment, so that differences in proton relaxation times within and among tissues are the source of contrast in MR images. In many clinical situations, the use of imaging agents allows better contrast to be obtained between healthy and pathological tissues. MRI contrast agents are not directly visualized in the image but only their effects are observed. The role of these agents is to shorten the longitudinal ( $T_1$ ) and/or transverse ( $T_2$ ) relaxation time of protons. Paramagnetic metals such as chelated gadolinium (III) ion have a strong effect on  $T_1$  relaxation while superparamagnetic nanoparticles affect the  $T_1$  and  $T_2/T_2^*$  relaxation times. The consequence is an improvement of the contrast between tissues. Recently, many papers have emphasized the development of nanoparticles as contrast agents (3). The advantages of the nanoparticles over the molecular contrast agents lies in their ability to amplify the MRI response (4), but also to gather in the same object several complementary properties. This attractive feature led to the development of multifunctional nanoparticles that can be detected by several *in vivo* imaging techniques. Among the

numerous possibilities, combining MRI and X-ray computed tomography (CT) is an attractive solution because not only are these modalities widely available in hospitals, but they also are complementary from a diagnostic point of view. It is therefore necessary to develop nanoparticles that could behave as contrast agents for both X-ray imaging and MRI. Designing such nanoparticles implies association within a nano-object, gadolinium (III) chelates as MRI contrast agents and high atomic number elements as contrast agents for X-ray CT imaging. In this context,

\* Correspondence to: F. Chuburu, Institut de Chimie Moléculaire de Reims, CNRS UMR 7312, UFR des Sciences Exactes et Naturelles, Bâtiment 18, Europol'Agro, BP 1039, 51687 REIMS Cedex 2, France. E-mail: francoise.chuburu@univ-reims.fr

a V. Mogilireddy, I. Déchamps-Olivier, F. Chuburu  
Institut de Chimie Moléculaire de Reims, CNRS UMR 7312, UFR des Sciences Exactes et Naturelles, Bâtiment 18, Europol'Agro, BP 1039, 51687 REIMS Cedex 2, France

b C. Alric, O. Tillement  
Laboratoire de Physico-Chimie des Matériaux Luminescents, UMR CNRS 5620, Université Claude Bernard Lyon 1, 69622 Villeurbanne Cedex, France

c G. Laurent, R. Bazzi, S. Roux  
Institut UTINAM, UMR 6213 CNRS, Université de Franche-Comté, 25030 BESANCON, France

d S. Laurent, L. Vander Elst, R. Muller  
University of Mons-Hainaut, NMR and Molecular Imaging Laboratory, Department of General, Organic and Biomedical Chemistry, B-7000 Mons, Belgium

e L. Vander Elst, R. Muller  
Center for Microscopy and Molecular Imaging, 6041 Gosselies, Belgium

gold nanoparticles were efficiently applied *in vivo* as X-ray contrast agents, because of the high atomic number of gold and high atomic absorption coefficient towards X-rays (5). Recently, gold nanoparticles functionalized by gadolinium (III) chelates were proposed as a bimodal contrast agent for CT/MRI (6–8). These particles were obtained by reducing a gold salt (9) in the presence of a dithiolated derivative of DTPA, namely DTDTPA (Scheme 1).

The ligand DTDTPA is a modified DTPA ligand for which two carboxylic functions were replaced by two amidothiol functions. If this modification is required to ensure the ligand grafting onto the gold nanoparticle, the thermodynamic stability and the kinetic inertness of the Gd–DTDTPA complex are expected to be lower since amido functions are less suited to a strong Gd<sup>3+</sup> coordination (10). Now, highly stable complexes are needed for *in vivo* applications to avoid problems associated with the release of toxic gadolinium (III) ions and development of Gd<sup>3+</sup>-related pathology (nephrogenic systemic fibrosis or NSF). Thus, in this context, it is necessary to determine the overall stability constants of DTDTPA (Scheme 1) and Au@DTDTPA (Scheme 1) towards Gd<sup>3+</sup>, and to evaluate the kinetic inertness of these two systems. In this work, we used potentiometric titrations to determine the Gd–DTDTPA and Gd–Au@DTDTPA stability constants by comparison with Gd–DTPA ones (Scheme 1) and we compared these constants with the ones determined towards potentially exchanging metals such as Zn<sup>2+</sup> or Ca<sup>2+</sup>. We also evaluate by means of relaxometric measurements the kinetic inertness of Gd–DTDTPA and Gd–Au@DTDTPA (11).

## 2. RESULTS AND DISCUSSION

### 2.1. DTDTPA and Au@DTDTPA Syntheses


As previously reported, DTDTPA was synthesized by addition of aminoethanethiol on diethylenetriaminepentacetic acid bis (anhydride) DTPA-BA in DMF, in the presence of triethylamine (6). The chelate-coated gold nanoparticles (Au@DTDTPA-Gd)

were synthesized as previously reported (6–8) by reducing a gold salt (HAuCl<sub>4</sub>·3H<sub>2</sub>O) with sodium borohydride (NaBH<sub>4</sub>) in the presence of DTDTPA (Scheme 1).


### 2.2. Acid–Base Behavior of DTDTPA and Au@DTDTPA

The acid–base behavior of DTDTPA and Au@DTDTPA was investigated through potentiometric titrations at 25 ± 0.1 °C by adding NMe<sub>4</sub>OH 0.1 mol l<sup>-1</sup>. The ionic strength was adjusted to 0.1 with NMe<sub>4</sub>Cl, the presence of hydrochloric acid allowing the protonation of the ligand. Protometric titrations could be depicted as curves of  $\bar{n}$  vs pH (Fig. 1), where  $\bar{n}$  is the average number of protons bounded per mole of ligand.

For DTDTPA (LH<sub>5</sub> in its neutral form), this curve showed a plateau in the pH range 5–8 for a  $\bar{n}$  value of 3. This indicated that, in this range, a sole triprotonated species LH<sub>3</sub><sup>-</sup> existed, which then could be stepwise deprotonated three times upon pH increase. For Au@DTDTPA (LH<sub>3</sub> in its neutral form), no plateau could be observed in this range, which indicated that for a grafted DTDTPA ligand, several species could co-exist in this pH range. The mathematical treatment of these data with PROTA software (12) allowed the determination of DTDTPA and Au@DTDTPA protonation constants [equation (2)] and the corresponding logK<sub>01h</sub> values are collected in Table 1. For DTDTPA, six protonation constants were determined. To analyze the protonation pattern of DTDTPA, the values determined for this ligand were compared with logK<sub>01h</sub> values of relevant ligands such as DTPA-BMA (13) (Table 1) or some thiolated ligands. A survey of a stability constants database (14) indicated that thiol functions exhibit higher protonation constants than amino groups. For instance, for 1, 2-ethanedithiol, they are respectively 10.43 and 9.00 (15), while for dimercaptosuccinic acid, thiol protonation constants are respectively 9.54 and 12.05 (16). For DTDTPA, the two first values (log K<sub>011</sub> = 10.37 and log K<sub>012</sub> = 9.77, Table 1) were similar to the protonation constants of this dithiol, suggesting that these two steps could be assigned to successive ionic equilibria

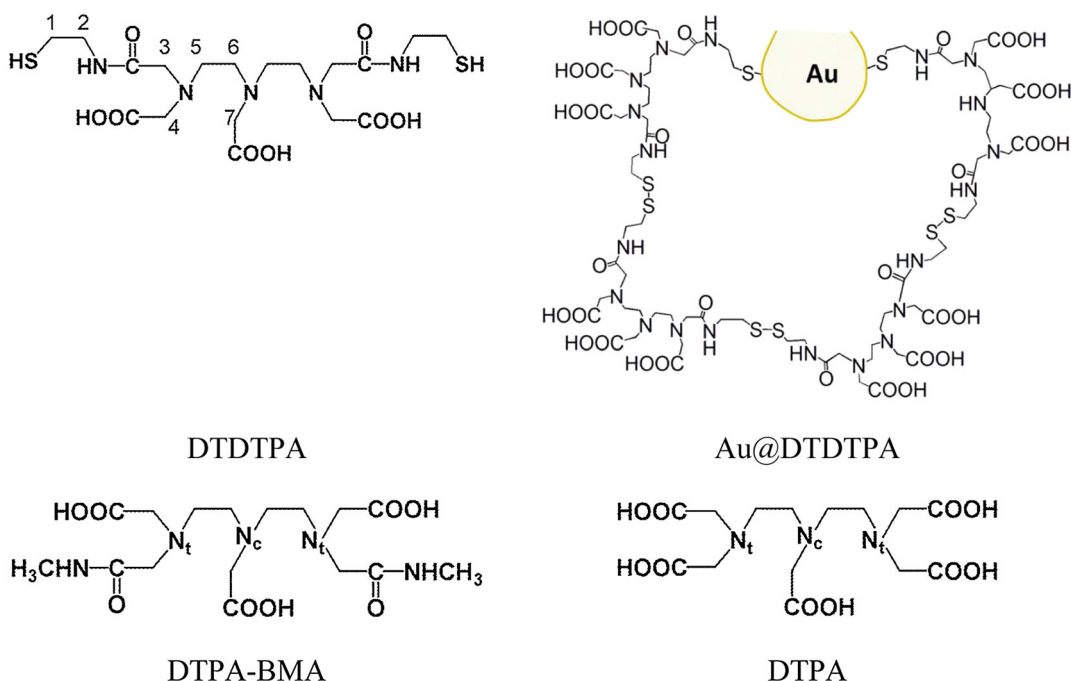


**Scheme 1.** Ligands DTDTPA, Au@DTDTPA [adapted from reference (6)], DTPA-BMA and DTPA.

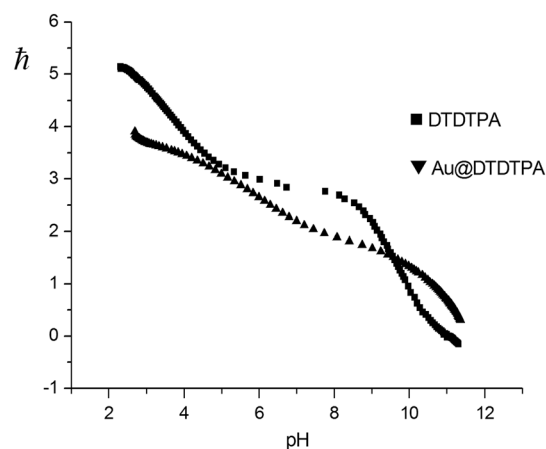

**Figure 1.** Average number  $\bar{h}$  of protons bound per mole of DTDTPA (solid square) and Au@DTDTPA (solid triangle) as a function of pH.

involving the two pendant RSH functions, successively deprotonated in two  $RS^-$  functions. This proposal can be supported by  $^1H$  NMR titration (Fig. 2). It is generally assumed that, when protonation occurs at a given nitrogen atom of a polyamine backbone, the  $^1H$  borne by the carbons in  $\alpha$  position to the nitrogen atom undergoes a downfield shift (17). From  $12 > pH > 8$  the  $H_1$  protons (Scheme 1) underwent a downfield shift from 2.3 to 2.7 ppm, in accordance with  $pK_a$  values determined by potentiometry. The four following constants could then involve the protonable sites of the DTPA bisamide backbone. For DTPA bisamides derivatives (13) and DTPA (14), it is well established that protonation equilibria measured in the pH range 9.5–3 take place at the backbone nitrogen atoms of the ligands. Thus for DTPA–BMA (13), the first proton ( $\log K_{011}=9.4$ , Table 1) is added at the central nitrogen atom  $N_c$  (Scheme 1) while the second ( $\log K_{012}=4.4$ ) and the third ( $\log K_{013}=3.1$ ) are added at the terminal nitrogen atoms ( $N_t$ , Scheme 1) (13). One should then observe that, for bisamide DTPA derivatives, a large  $\Delta\log K_{12} = \log K_{011} - \log K_{012}$  value is expected and this difference is greatly superior to the one in the parent DTPA ligand ( $\Delta\log K_{12} = 10.41 - 8.37$ ). For DTDTPA, this criterion is fulfilled between  $\log K_{013}$  (8.96) and  $\log K_{014}$  (4.79). This result, similar to what was measured for DTPA bisamide conjugate of penicillamine grafted onto Au nanoparticles (18,19), suggested that the third proton was added on the central nitrogen atom of DTDTPA.  $^1H$  NMR titration supported this assumption since the addition

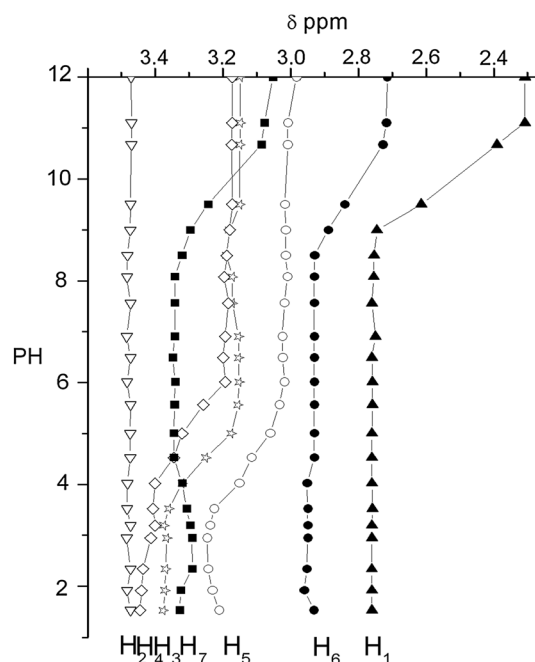

**Figure 2.**  $^1H$  NMR titration of DTDTPA.


of the third proton ( $10 > pH > 8$ ) was accompanied by the simultaneous downfield shifts of  $H_6$  and  $H_7$  (Fig. 2). Concerning  $\log K_{014}$  and  $\log K_{015}$  protonation events, they could be assigned to the terminal backbone nitrogen atoms,  $^1H$  NMR titration indicating that the addition of the two corresponding protons ( $6 > pH > 3$ ) induced a downfield shift for  $H_3$ ,  $H_4$  and  $H_5$  resonances. Finally, the last constant ( $\log K_{016}$ ) could be attributed to the protonation of a carboxylate oxygen. By analogy with DTPA bisamide derivatives, one can propose that this carboxylate group could be borne by the central backbone nitrogen. On the basis of these propositions, the protonation pattern of DTDTPA could be described as in Scheme 2.

For Au@DTDTPA, five protonation constants were determined. FT-IR and XPS analysis of Au@DTDTPA (6) revealed that DTDTPA is anchored at the nanoparticle surface by one thiol group and the unreacted thiols established disulfide bonds between neighboring DTDTPA (Scheme 1). As a result, DTDTPA led to the formation of a multilayered ligand shell (6). Owing to DTDTPA packing at the nanoparticle surface, all the protonation events that could be determined by potentiometry experiments are

**Table 1.** Protonation constants of DTDTPA and Au@DTDTPA (25 °C, 0.1 M  $NMe_4Cl$ , Ar). Standard deviations are shown in parentheses

$\log K_{01h}$	DTDTPA	DTPA-BMA <sup>a</sup>	Au@DTDTPA	DTPA <sup>b</sup>
[LH]/[L][H <sub>3</sub> O <sup>+</sup> ]	10.37 (2)	9.4	11.26 (3)	10.41
[LH <sub>2</sub> ]/[LH][H <sub>3</sub> O <sup>+</sup> ]	9.77 (1)	4.4	10.12 (2)	8.37
[LH <sub>3</sub> ]/[LH <sub>2</sub> ][H <sub>3</sub> O <sup>+</sup> ]	8.96 (2)	3.1	7.27 (3)	4.09
[LH <sub>4</sub> ]/[LH <sub>3</sub> ][H <sub>3</sub> O <sup>+</sup> ]	4.79 (1)	—	5.75 (2)	2.51
[LH <sub>5</sub> ]/[LH <sub>4</sub> ][H <sub>3</sub> O <sup>+</sup> ]	3.43 (1)	—	3.78 (1)	2.04
[LH <sub>6</sub> ]/[LH <sub>5</sub> ][H <sub>3</sub> O <sup>+</sup> ]	2.34 (1) <sup>c</sup>	—	—	—
$\Sigma \log K_{01-5}$	37.32	15.78	38.18	27.42

<sup>a</sup>Reference (13) (0.1 M NaCl);  
<sup>b</sup>reference (14) (0.1 M KCl);  
<sup>c</sup>not included in  $\Sigma \log K_{01-5}$  calculation.

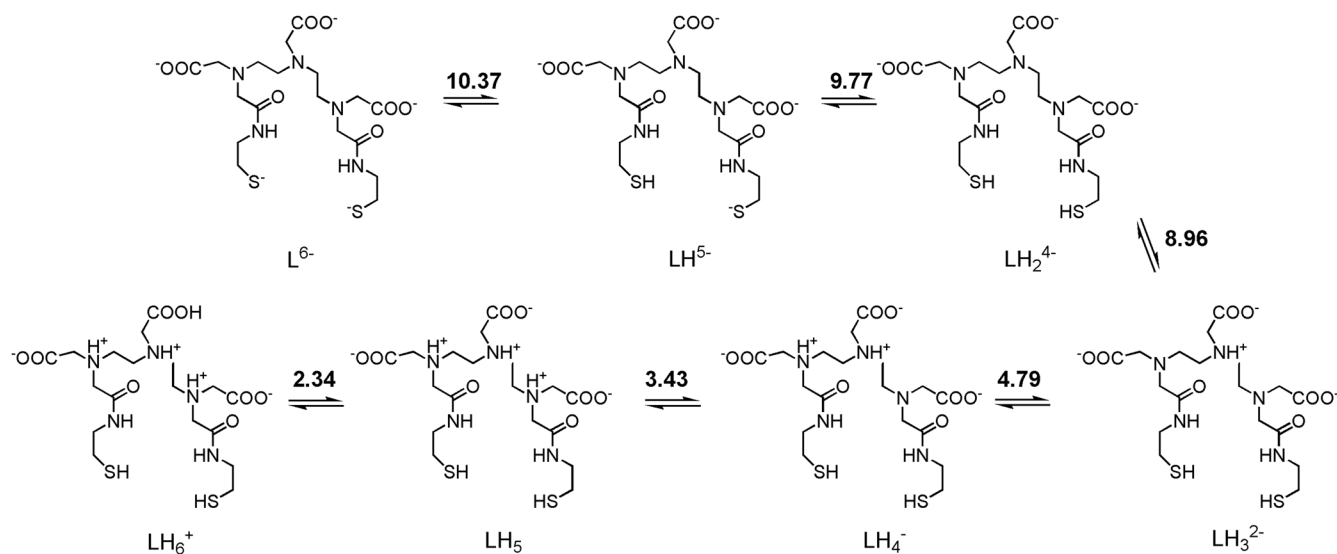


**Scheme 2.** Protonation pattern of DTDTPA.

the result of overall proton exchanges. Therefore, these equilibria are studied by measuring the average number of protons released for a fixed amount of grafted nanoparticles.


Comparison of Au@DTDTPA backbone nitrogen atom deprotonation constant values ( $\log K_{011}$  to  $\log K_{013}$ ) with those of DTDTPA showed that, in a general trend, the basicity of the amino nitrogen atoms increased when the ligand was anchored at the nanoparticle surface. This basicity enhancement could be interpreted as the result of H-bonds between the added protons and all the acido-basic sites. Indeed, owing to the ligand packing at the nanoparticle surface, these sites were spread all around the nano-object and could stabilize these protons. These results were similar to the ones reported for polyaminocarboxylate ligands embedded on the surface of macromolecules, for which the existence of an extended hydrogen bond network alters the overall charge distribution at the vicinity of these ligands and modifies their basicity (20). As a consequence, the identification of the protonation sites at the surface of the functionalized nanoparticle, that is to say a site-specific description of the nanoparticle protonation, was rather speculative since, first, the accessibility of acido-basic functions was probably not homogenous at the surface and second, successive additions of protons were probably followed by ligand reorganization at the surface (21).

### 2.3. Stability Constants and Thermodynamic Stability of DTDTPA:Gd and Au@DTDTPA:Gd

To evaluate the thermodynamic stability of  $\text{Gd}^{3+}$  complexes with DTDTPA and Au@DTDTPA, the overall stability constants of DTDTPA:Gd and Au@DTDTPA:Gd systems were determined by potentiometry. For DTDTPA: $\text{Gd}^{3+}$  system (Fig. 3), the comparison of  $\bar{h}$  vs pH curves for the ligand alone and in the presence of  $\text{Gd}^{3+}$  ions (metal-to-ligand ratio  $R \approx 1$ ) showed that, in the presence of  $\text{Gd}^{3+}$ , the titration curve was depressed relative to the titration curve of the ligand alone. This deviation revealed complex formation from pH 2.5. The DTDTPA: $\text{Gd}^{3+}$  curve presented a plateau for  $4 < \text{pH} < 8$  and  $\text{pH} > 11$  for  $\bar{h} = 2$  and 0, respectively. The first plateau corresponded to the existence in solution of a diprotonated complex ( $\text{GdLH}_2$  species) while the second one could be correlated with the existence of a deprotonated species

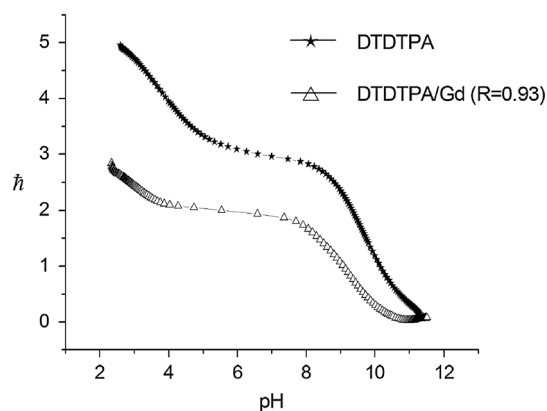

**Figure 3.** Average number  $\bar{h}$  of protons bound per mole of DTDTPA (\*) and DTDTPA:Gd (open triangle) as a function of pH.

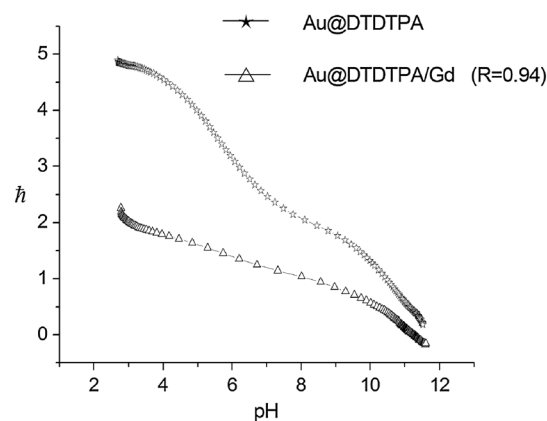

**Figure 4.** Average number  $\bar{h}$  of protons bound per mole of Au@DTDTPA (\*) and Au@DTDTPA:Gd (open triangle) as a function of pH.

( $\text{GdL}^{2-}$ ). For the Au@DTDTPA: $\text{Gd}^{3+}$  system (Fig. 4), the comparison of  $\bar{h}$  vs pH curves for the grafted Au nanoparticle alone and in the presence of  $\text{Gd}^{3+}$  ions ( $R \approx 1$ ) showed that complexation occurred also from pH 2.5. The shape curve between  $6 < \text{pH} < 9$





**Table 2.** Stability constants for DTDTPA:M and Au@DTDTPA: M systems ( $C_L = C_M = 2.0 \times 10^{-3} \text{ mol l}^{-1}$ )

$\log \beta_{m1h}$	L = DTDTPA	L = Au@DTDTPA
$L + 2H^+ + Gd^{3+} = GdLH_2$	34.94 (4)	35.6 (2)
$L + H^+ + Gd^{3+} = GdLH$	26.41 (5)	31.7 (2)
$L + Gd^{3+} = GdL$	16.46 (5)	21.2 (2)
$\log K_{m1h}$		
$GdL + H = GdLH$	9.95	10.5
$GdLH + H = GdLH_2$	8.53	3.9


for an  $\bar{h}$  value of 1 suggested the existence in solution of a monoprotonated complex ( $Au@GdLH^+$  species). Data analysis by PROTAF software (12) indicated that, for DTDTPA:Gd<sup>3+</sup> and Au@DTDTPA:Gd<sup>3+</sup> systems, the best curve fitting is obtained by assuming the formation of GdLH<sub>2</sub>, GdLH and GdL complexes (charges of the complexes omitted here for clarity), whose overall formation constants are reported in Table 2. DTDTPA exhibited eight potential donor atoms to coordinate Gd<sup>3+</sup> and the similarity of the two successive deprotonation constant values of GdLH<sub>2</sub> ( $\log K = 9.95$  and  $8.57$ ) with the two first deprotonation constants of DTDTPA alone ( $\log K_{011} = 10.37$  and  $\log K_{012} = 9.77$ ) suggested that, in GdLH<sub>2</sub>, the successive deprotonations into GdLH<sup>-</sup> and GdL<sup>2-</sup> involved the thiol functions. These functions are not expected to coordinate to the Gd<sup>3+</sup> ion (22). However, the two deprotonation SH/S<sup>-</sup> equilibria occurred at lower pH in DTDTPA:Gd than in the ligand alone, which could be interpreted as an assistance of the metal to the complex deprotonation. The species distribution diagrams of DTDTPA:Gd and Au@DTDTPA:Gd systems are reported in Fig. 5. It was also important to compare the stability of these Gd complexes with the ones of potentially competitive endogenous ions such as Zn<sup>2+</sup> and Ca<sup>2+</sup>. It is indeed well known that Zn<sup>2+</sup> ions can behave as an exchanging metal towards Gd<sup>3+</sup> (11,23). In addition, Ca<sup>2+</sup> and Gd<sup>3+</sup> possess similar ionic radii, leading to potential exchanges *in vivo* (24). The overall complexation constants of DTDTPA:M and Au@DTDTPA:M with M = Zn<sup>2+</sup>, and Ca<sup>2+</sup> are reported in Tables S1 and S2 (Supporting Information). The trend of increasing complex stability is Ca<sup>2+</sup> < Zn<sup>2+</sup> < Gd<sup>3+</sup>. One should note that, for DTDTPA:Ca systems, thiol groups are not expected to coordinate Ca<sup>2+</sup> and their deprotonation should not be significantly influenced by the coordination of Ca<sup>2+</sup> to the ligand. Indeed, from pH-potentiometric titrations two constants corresponding to  $\log K_{CaLH} = 10.2$  and  $\log K_{CaLH_2} = 8.9$  were obtained (Table S2, Supporting Information), values relatively close to the  $\log K_{011} = 10.37$  and  $\log K_{012} = 9.77$  (Table 1) determined for the ligand itself.

To circumvent the different protonated states of the complexes, an efficient way to compare the sequestering ability of DTDTPA and Au@DTDTPA for all these ions was to determine the logarithmic amount of free metal relative to the metal coordinated on the whole pH range. Thus, the smallest the logarithmic value is, the higher is the affinity of the ligand for the metal ion. For Gd<sup>3+</sup> first (Fig. 6), the DTDTPA:Gd complex was less stable than Au@DTDTPA:Gd, this latter being 2 orders of magnitude more stable at physiological pH. This result was in the expected relation to the previously measured enhancement of DTDTPA basicity when it was grafted on the Au nanoparticle. Second, the comparison of DTDTPA and Au@DTDTPA affinities for the three metal ions (Fig. 7) indicated that for each of them the best affinity was obtained for Gd<sup>3+</sup>, which is a crucial point for the use of these systems as MRI contrast agents.

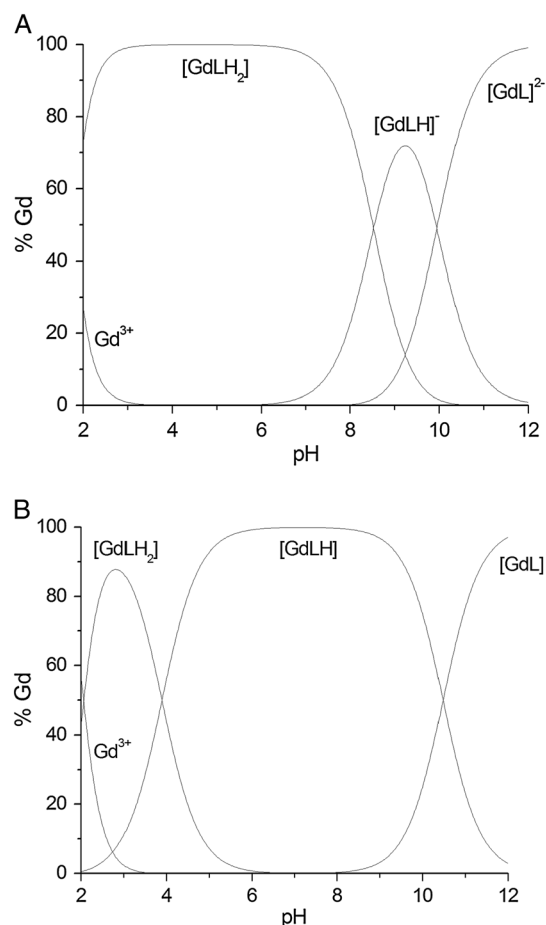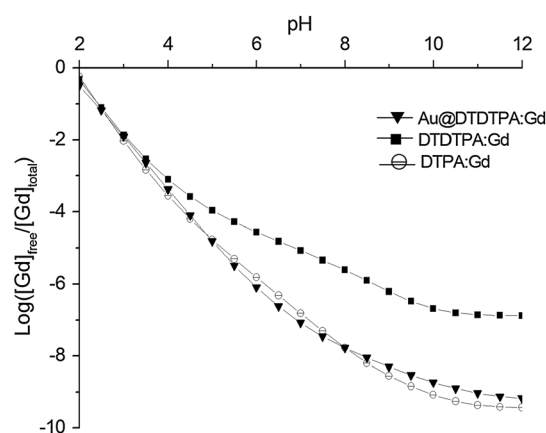**Figure 5.** Species distribution diagrams for Gd(III) complexes with (a) DTDTPA, (b) Au@DTDTPA ( $C_L = C_M = 2.0 \times 10^{-3} \text{ mol l}^{-1}$ ).**Figure 6.**  $[Gd]_{\text{free}}/[Gd]_{\text{total}}$  for DTDTPA and Au@DTDTPA systems in comparison with DTPA.


#### 2.4. Transmetalation of DTDTPA:Gd and Au@DTDTPA:Gd

Since both Gd<sup>3+</sup> and polyaminocarboxylate ligands are toxic, DTDTPA:Gd and Au@DTDTPA:Gd must have high kinetic inertness, which means that the extent of their dissociation in the body has to be practically negligible. The previous results indicated that overall stability constants of Zn<sup>2+</sup> complexes were close to those of Gd<sup>3+</sup>, suggesting that Zn<sup>2+</sup> could act as an

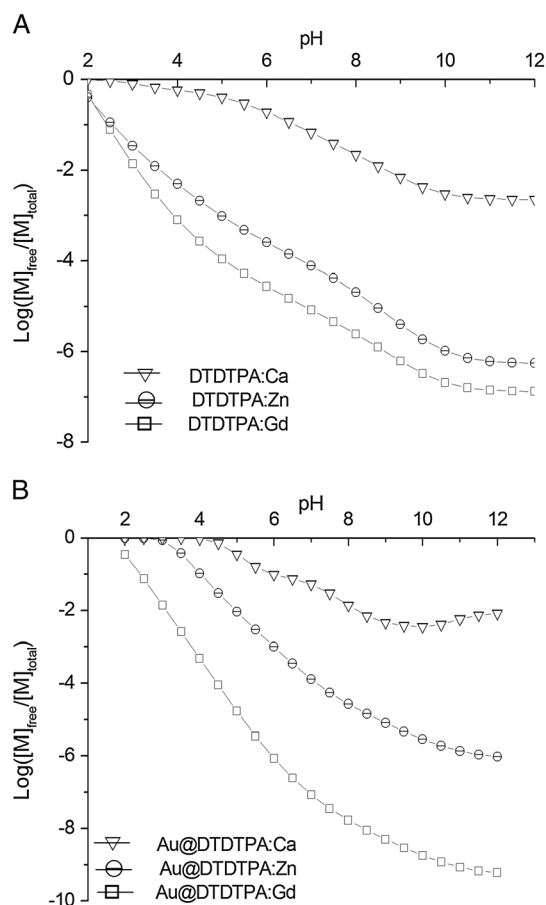


**Figure 7.**  $[M]_{\text{free}}/[M]_{\text{total}}$  for (a) DTDTPA and (b) Au@DTDTPA systems with  $M = \text{Gd(III)}$ ,  $\text{Zn(II)}$  and  $\text{Ca(II)}$ .

exchanging metal in biological media. The kinetic stabilities of DTDTPA:Gd and Au@DTDTPA:Gd were characterized by the rate of their transmetallation reaction occurring in solution with  $\text{Zn}^{2+}$  ions and, for a direct comparison, the same method was used for DTPA:Gd. [The aim of the study being a direct comparison of the respective kinetic inertness of DTDTPA:Gd and Au@DTDTPA:Gd, exchange reactions with  $\text{Cu(II)}$  were not considered here. Actually, it was not possible to follow by UV-vis spectroscopy the transmetallation reaction with this ion in the case of Au@DTDTPA:Gd, because of strong absorption of the nanosuspension.] It has indeed been proposed that the kinetic stability of a  $\text{Gd}^{3+}$  chelate can be followed by relaxometry in the presence of  $\text{Zn}^{2+}$  in a phosphate-buffered solution (11). If the transmetallation reaction occurs, it will result in  $\text{Gd}^{3+}$  release which then will precipitate into  $\text{GdPO}_4$ . Consequently, it will lead to a subsequent decrease of the proton paramagnetic relaxation rate ( $R_{1p}$ ) (11). DTDTPA:Gd and Au@DTDTPA:Gd  $R_{1p}$  evolutions with time gave therefore a good estimation of transmetallation. Fig. 8 showed the evolution of their normalized paramagnetic relaxation rates  $R_{1p}^t/R_{1p}^0$  and compared them with those of DTPA:Gd. A semi-quantitative evaluation of the transmetallation kinetics was performed by comparing the time needed to reach 80% of the initial  $R_{1p}^0$  value. The shortest delay was obtained for DTDTPA:Gd (110 min) while for Au@DTDTPA:Gd the delay was similar to that measured for DTPA:Gd (220 min). These results favored the kinetic inertness of Au@DTDTPA:Gd system. A theoretical description was attempted to evaluate in the current experimental conditions the rate of transmetallation of the  $\text{Gd}^{3+}$

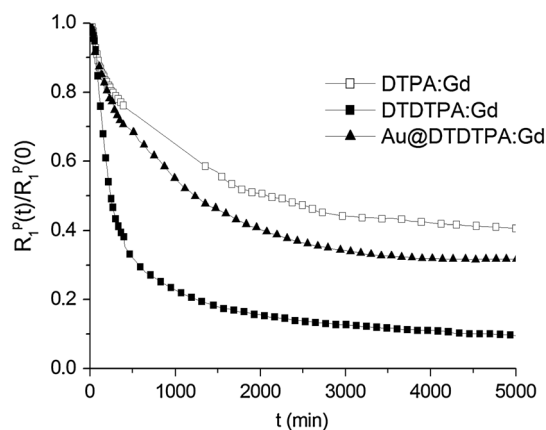

**Figure 8.** Evolution of  $R_{1p}(t)/R_{1p}^0$  vs time for DTPA:Gd, DTDTPA:Gd and Au@DTDTPA:Gd (initial concentrations of Gd complexes and  $\text{ZnCl}_2 \cdot 2.5$  mM in phosphate buffer  $\text{pH} = 7$ ,  $T = 37^\circ\text{C}$ ,  $B = 0.94$  T).

species and the  $\text{Gd}^{3+}$  species lifetimes [equations (4) and (5)]. The  $k_{\text{obs}}$  values obtained by fitting the experimental data were  $3.9 \times 10^{-3}$  and  $2.7 \times 10^{-3} \text{ min}^{-1}$  for DTDTPA:Gd and Au@DTDTPA:Gd, respectively, while for the reference DTPA:Gd this constant was  $2.5 \times 10^{-3} \text{ min}^{-1}$ . Therefore, DTDTPA:Gd and Au@DTDTPA:Gd half-life values were 177 and 257 min, respectively, while for the reference DTPA:Gd the half-life was 277 min. At the end of the observation period ( $\sim 3$  days) the ratio  $R_{1p}^t/R_{1p}^0$  was about 10% for DTDTPA:Gd compared with 50% for the reference DTPA:Gd. This indicated that the bisamide complex DTDTPA:Gd showed more extensive transmetallation than the parent compound. This behavior was consistent with what was already determined in GdDTPA bisamide series (25,26). The reason for this lies in the substitution of two carboxylate groups by two amide groups in the first coordination sphere of  $\text{Gd}^{3+}$ . For Au@DTDTPA:Gd the ratio of  $R_{1p}^t/R_{1p}^0$  was remarkably higher (33%) and comparable to that of the reference DTPA:Gd. This indicated that, when DTDTPA:Gd is grafted onto the Au nanoparticle, its transmetallation tends to be reduced. This behavior was also reported in a bisamide DTPA series for which the amide hydrogen atoms were gradually substituted with butyl groups, which induced a steric hindrance at the vicinity of the Gd center (27). The similar result obtained here suggested that the bulky nanoparticle rigidified the structure of the complex and

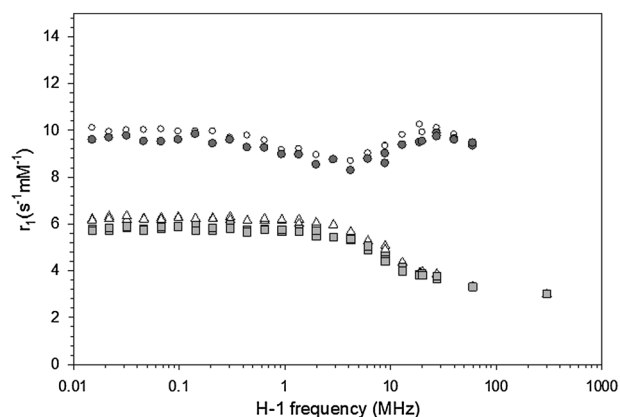

**Figure 9.** NMRD profile of Au@DTDTPA:Gd nanoparticles: (open circle)  $t = 0$ ; (solid circle)  $s = 7$  days later [Magnevist® (open triangle) and GdDTDTPA (solid circle) NMRD profiles are given for comparison.]

prevented grafted DTDTPA:Gd complexes from extensive demetallation. To follow the nanosuspension relaxivity, NMRD profiles of a nanosuspension for which a third of DTDTPA ligands were complexed were recorded over a period of 7 days (Fig. 9). Compared with DTDTPA:Gd and DTPA:Gd complexes, these profiles were characterized by a maximum in relaxivity between 10 and 100 MHz typical of slowly rotating complexes of  $Gd^{3+}$ . Furthermore, the perfect superimposition of the two profiles for Au@DTDTPA:Gd at days 0 and 7 highlighted that no  $Gd^{3+}$  leakage could be detected. This result showed the very good stability of this nanosuspension. Moreover, since Au@DTDTPA:Gd elimination by renal filtration is rapid (25 min after intravenous injection) (7), this result constitutes a positive argument for the use of these nanoparticles *in vivo*.

### 3. CONCLUSION

Gold nanoparticles coated by a dithiolated bisamide ligand DTDTPA (Au@DTDTPA), elaborated for both X-ray and MRI imaging, have been evaluated in terms of thermodynamic stability and kinetic inertness of their  $Gd^{3+}$  complex. This study was motivated by the fact that stability and toxicity issues of Gd-based contrast agents might be associated with the use of certain DTPA-bisamide derivative  $Gd^{3+}$  complexes. For that reason, potentiometric titrations and relaxometric measurements were performed on DTDTPA alone, and Au@DTDTPA, and the results compared with those of the parent DTPA ligand. The decreased basicity of the backbone nitrogens brought by amide formation in DTDTPA was modified when the ligand was grafted on the Au nanoparticle, which resulted in an enhancement of the thermodynamic stability of the corresponding Au@DTDTPA:Gd complex by comparison with DTDTPA:Gd. Therefore, the grafted DTDTPA:Gd gained in stability, leading to a complex almost as stable as DTPA:Gd itself. Moreover, comparison of Au@DTDTPA affinity towards  $Gd^{3+}$ -competitive ions, namely  $Zn^{2+}$  and  $Ca^{2+}$ , showed that the best affinity was obtained for  $Gd^{3+}$ . Transmetallation of Au@DTDTPA:Gd in the presence of  $Zn^{2+}$ , the most abundant endogenous metal ion, was then undertaken to evaluate the kinetic stability of the metallated gold nanoparticle, close to physiological conditions. These conditions, although different from the *in vivo* ones, provided information concerning the *in vivo* kinetic behavior of the complexes. The stability of the immobilized chelates regarding transmetallation against  $Zn^{2+}$  was evaluated by relaxometric measurements using the protocol established for soluble  $Gd^{3+}$  chelates. The time evolution of Au@DTDTPA:Gd relaxivity suggested that transmetallation was a slightly perceptible than for DTPA:Gd. Nevertheless, the extent of the demetallation was distinctly less important than for the nongrafted DTDTPA:Gd and could be prevented by finding a good compromise between amounts of chelated  $Gd^{3+}$  at the nanoparticle surface and colloidal stability while providing an enhancement of relaxivity.

## 4. EXPERIMENTAL

### 4.1. General

#### 4.1.1. DTDTPA synthesis

DTDTPA synthesis was previously described (6–8). In a round flask of 250 ml, 2 g ( $5.6 \times 10^{-3}$  mol) of diethylenetriaminepentaacetic acid bis-anhydride was dissolved in 40 ml of dimethylformamide

and then heated to 70 °C. In another flask, 1.4 g ( $1.23 \times 10^{-2}$  mol) of aminoethanethiol was dissolved in 30 ml of DMF and 1.74 ml of triethylamine. This solution was added to the round flask and stirring magnetically at 70 °C overnight. Then, the solution was first cooled to room temperature and then put into an ice bath. A white powder ( $NEt_3$ , HCl) precipitated and was filtered. The filtrate was concentrated at low pressure. After addition of this solution to a chloroform solution, a white precipitate was formed. After filtration of solution, washing with 50 ml of chloroform and drying under vacuum, DTDTPA was obtained as white powder (90% yield).

$^1H$  NMR (300 MHz,  $D_2O$ , 298 K):  $\delta$ : 3.81 (s, 4H, -N-CH<sub>2</sub>-CO-N-), 3.69 (s, 4H, -N-CH<sub>2</sub>-COOH), 3.64 (s, 2H, -N-CH<sub>2</sub>-COOH), 3.38–3.20 (m, 12H, -N-CH<sub>2</sub>-CH<sub>2</sub>-SH, -N-CH<sub>2</sub>-CH<sub>2</sub>-N), 2.70 (t, 4H, N-CH<sub>2</sub>-CH<sub>2</sub>-SH).  $^{13}C$  NMR (75 MHz,  $D_2O$ , 298 K):  $\delta$ : 172.48 and 172.18 (-N-CH<sub>2</sub>-COOH), 168.93 (-N-CH<sub>2</sub>-CO-N), 57.17 and 56.86 (-N-CH<sub>2</sub>-COOH), 54.76 (N-CH<sub>2</sub>-CO-N), 52.17 and 51.55 (-N-CH<sub>2</sub>-CH<sub>2</sub>-N), 42.61 (-N-CH<sub>2</sub>-CH<sub>2</sub>-SH), 23.68 (-N-CH<sub>2</sub>-CH<sub>2</sub>-SH).

IR: 2929 ( $\nu_{CH}$ , alkyl), 2530 ( $\nu_{SH}$ ), 1718 ( $\nu_{CO}$ , COOH), 1646 ( $\nu_{CO}$ , RCONR'), 1533 ( $\nu_{CO}$ , RCONHR')  $cm^{-1}$ . The comparison of spectra of DTPA and DTDTPA show clearly the emergence of a characteristic peak for  $\nu_{S-H}$  at  $2530\text{ cm}^{-1}$ . ES-MS (+):  $m/z$  = 512 ( $[M + H]^+$ ); 534.2 ( $[M + Na]^+$ ).

#### 4.1.2. $^1H$ NMR titration

The pH was adjusted by additions of small amounts of a 1 M NaOH or 1 M HCl solution to  $H_2O$  solutions (with 10%  $D_2O$  and 2,2-dimethyl-2-silapentane-5-sulfonate sodium salt as a calibration standard) containing DTDTPA ( $1.3 \times 10^{-2}\text{ mol l}^{-1}$ ) under argon atmosphere. NMR measurements were performed on a Bruker AIII 600 (600.16 MHz) after an equilibration time of 1 day.

#### 4.1.3. Au@DTDTPA:Gd synthesis

For a typical preparation of gold particles (6–8), 200 mg ( $51 \times 10^{-5}$  mol) of  $HAuCl_4 \cdot 3H_2O$ , dissolved in 60 ml of methanol, was placed in a 250 ml round-bottom flask. A 256 mg ( $50 \times 10^{-5}$  mol) aliquot of DTDTPA in 40 ml of water and 2 ml of acetic acid was added to the gold salt solution under stirring. The mixture turned from yellow to orange. After 5 min, 185 mg ( $489 \times 10^{-5}$  mol) of  $NaBH_4$  dissolved in 14 ml of water was added to the orange mixture under vigorous stirring at room temperature. At the beginning of the  $NaBH_4$  addition, the solution became first dark brown then a black flocculate appeared. The vigorous stirring was maintained for 1 h before adding 5 ml of 1 M aqueous hydrochloric acid solution. After the partial removal of the solvent under reduced pressure and at a maximum of 40 °C, the precipitate was filtered on a polymer membrane and washed thoroughly and successively with 0.01 M HCl, water and diethylether. The resulting black powder (Au@DTDTPA) was dried and stocked in the solid state or dispersed in 10 ml of 0.01 M NaOH solution (up to 200 mg of dry powder).

#### 4.1.4. Au@DTDTPA:Gd<sub>50</sub> synthesis


For  $^1H$  NMRD profile measurements, the ligand-to-metal ratio was fixed to 3.  $Gd^{3+}$  complexation was carried out through the addition of  $GdCl_3$  (102  $\mu$ l,  $[Gd^{3+}] = 135\text{ mM}$ ) on Au@DTDTPA colloidal solution (2232  $\mu$ l,  $[Au] = 45\text{ mM}$ ) under stirring at room temperature at pH 4.



## 4.2. Potentiometric Titrations


Potentiometric titrations were carried out in the pH range 2–11 with an automatic titrator composed of a microprocessor buret Metrohm dosimat 665 and a pHmeter Metrohm 713 connected to a computer. The titration procedure was fully automated (12). All measurements were performed within a thermoregulated cell at  $25.0 \pm 0.1$  °C under an argon stream to avoid the dissolution of carbon dioxide. The ionic strength was adjusted to 0.1 with  $N(\text{Me})_4\text{Cl}$ . The combined Type 'U' glass electrode Metrohm used had a very low alkaline error. The  $pK_w$  was fixed at 13.78 for all analyses. Stock solutions of metal ions were prepared from analytical-grade salts ( $\text{GdCl}_3$ ,  $5.07 \times 10^{-2} \text{ mol l}^{-1}$ ;  $\text{ZnCl}_2$ ,  $10^{-1} \text{ mol l}^{-1}$ ;  $\text{CaCl}_2$ ,  $7.97 \times 10^{-2} \text{ mol l}^{-1}$ ; Aldrich 99.9%). The concentrations of each metal stock solution were determined by EDTA. Before their utilization, the mother solutions were diluted and ionic strength was adjusted to 0.1 with  $N(\text{Me})_4\text{Cl}$ . Solutions of  $L = \text{DTDTPA}$  ( $2 \times 10^{-3} \text{ mol l}^{-1}$ ) and  $\text{Au@DTDTPA}$  ( $1.5 \times 10^{-3} \text{ mol l}^{-1}$ ) were titrated under Ar with standardized  $N(\text{Me})_4\text{OH}$  solution ( $5 \times 10^{-2} \text{ mol l}^{-1}$ ). For complexation studies, several ligand/metal ratios ( $[\text{L}]/[\text{M}]$ ) were used:  $1.05 < [\text{L}]/[\text{M}] < 1.8$  ( $L = \text{DTDTPA}$  or  $\text{Au@DTDTPA}$ ) and  $8 \times 10^{-4} < [\text{L}] < 1.2 \times 10^{-3} \text{ mol l}^{-1}$ , each ratio being calculated on the basis of the concentrations of ligand and metal solutions previously determined, and their respective volumes. For each titration, the total volume in the cell was 4 ml.

The protometric data were processed using the PROTAF program (12) to obtain the best fit chemical model and refined overall constants  $\beta_{\text{mlh}}$  (except for the proton; the charges are not shown for clarity reasons):



$$\beta_{\text{mlh}} = \frac{[\text{M}_m\text{L}_\ell\text{H}_h]}{[\text{M}]^m [\text{L}]^\ell [\text{H}^+]^h} \quad (1)$$

The stepwise protonation constants ( $K_{0\ell h}$ ) related to equilibrium (II) and defined by equation (2) were deduced from the refined ( $\beta_{0\ell h}$ ) values by equation (3):



$$K_{0\ell h} = \frac{[\text{LH}_h]}{[\text{LH}_{h-1}] [\text{H}^+]} \quad (2)$$

$$\beta_{0\ell h} = \prod_{i=1}^h K_{0\ell i} \quad (3)$$

Each titration used at least 150 points per neutralization curve, and titrations were repeated until a satisfactory agreement was reached. A minimum of 10 curves were used for the determination of the DTDTPA and  $\text{Au@DTDTPA}$  protonation constants. The titration data were fitted to a model of a ligand with six and five ionizable groups for DTDTPA and  $\text{Au@DTDTPA}$  respectively, using the program PROTAF (12). For the determination of the complexation constants, two curves were used for each  $[\text{L}]/[\text{M}]$  ratio (leading to a minimum of 10 curves for each ligand). The stability constants were determined by analysis of the titration curves with PROTAF (12). The  $\text{Gd}^{3+}$  data was fit to a model containing three species,  $\text{GdLH}_2$ ,  $\text{GdLH}$  and  $\text{GdL}$ . The  $\text{Zn}^{2+}$  data was modeled with five metal–ligand species –  $\text{ZnLH}_3$ ,  $\text{ZnLH}_2$ ,  $\text{ZnLH}$ ,

$\text{ZnL}$  and  $\text{ZnL}(\text{OH})$  – while the  $\text{Ca}^{2+}$  data was fitted to a model that considered five species –  $\text{CaLH}_4$ ,  $\text{CaLH}_3$ ,  $\text{CaLH}_2$ ,  $\text{CaLH}$  and  $\text{CaL}$ . Speciation curves were obtained with HYSS program (28); afterwards  $\log [(M_{\text{free}})/(M_{\text{total}})]$  values were deduced under the following conditions:  $[\text{L}] = [\text{M}] = 2.0 \times 10^{-3} \text{ mol l}^{-1}$ .

## 4.3. Transmetallation Process

The reactions of  $\text{DTDTPA}:\text{Gd}$ ,  $\text{Au@DTDTPA}:\text{Gd}$  and  $\text{DTPA}:\text{Gd}$  with  $\text{Zn}^{2+}$  were monitored by measuring the longitudinal relaxation rates  $R_1$  ( $1/T_1$ ) of water protons on a Bruker mq40 Minispec relaxometer (0.94 T), by the inversion recovery method. A  $12.8 \mu\text{l}$  aliquot of a  $1.46 \times 10^{-1} \text{ mol l}^{-1}$  solution of  $\text{ZnCl}_2$  was added to  $750 \mu\text{l}$  of a phosphate-buffered (pH 7) solution of the paramagnetic complex ( $2.5 \times 10^{-3} \text{ mol l}^{-1}$ ). The mixture was stirred and  $75 \mu\text{l}$  was taken off for relaxometry. The  $R_{1p}$  relaxation rate was obtained after subtraction of the diamagnetic contribution of the proton water relaxation ( $0.2656 \text{ s}^{-1}$ ) from the observed relaxation rate  $R_{1p}^t$ . The temperature was equilibrated and maintained at 37 °C during the experiments. In preliminary experiments, it was checked that the buffer itself was unable to extract  $\text{Gd}^{3+}$  from  $\text{DTDTPA}:\text{Gd}$ ,  $\text{Au@DTDTPA}:\text{Gd}$  and  $\text{DTPA}:\text{Gd}$  respectively.

The rate of the reactions can be expressed as shown in equation (4):

$$-d[\text{GdL}]_t/dt = k_{\text{obs}}[\text{GdL}]_t \quad (4)$$

where  $[\text{GdL}]_t$  is the total concentration of the complex ( $L = \text{DTDTPA}$ ,  $\text{Au@DTDTPA}$ ,  $\text{DTPA}$ , respectively). Under our experimental conditions (phosphate buffer, pH 7), the concentration of free  $\text{Zn}^{2+}$  is assumed to be approximately constant. Effectively, this concentration is ruled by the solubility constant of  $\text{Zn}_3(\text{PO}_4)_2$  and as soon as  $\text{Zn}^{2+}$  is consumed by the transmetallation reaction it is regenerated by dissolution of  $\text{Zn}_3(\text{PO}_4)_2$  (24). Consequently, the rate of transmetallation  $k_{\text{obs}}$  was determined using equation (5), where  $R_{1p}^0$ ,  $R_{1p}^t$  and  $R_{1p}^e$  are the relaxation rate values at the start, at time  $t$  and at equilibrium of the reaction:

$$R_{1p}^t = R_{1p}^e + (R_{1p}^0 - R_{1p}^e) \exp(-k_{\text{obs}}t) \quad (5)$$

## 4.4. NMRD Profile

$^1\text{H}$  NMRD profiles were measured on a Stelar Spinmaster FFC fast field cycling NMR relaxometer (Stelar, Mede, Pavia, Italy) over a range of magnetic fields extending from 0.24 mT to 0.7 T and corresponding to  $^1\text{H}$  Larmor frequencies from 0.01 to 40 MHz using 0.6 ml samples in 10 mm o.d. tubes. The temperature was kept constant at 37 °C. The additional relaxation rate at 60 MHz was obtained with a Bruker Minispec mq60 spectrometer (Bruker, Karlsruhe, Germany).

## Acknowledgements

V. Mogilireddy thanks the Region Champagne Ardenne for her doctoral fellowship. Agathe Martinez is gratefully acknowledged for her help in  $^1\text{H}$  NMR titration. Financial support by CNRS, Conseil Regional Champagne Ardenne, Conseil General de la Marne, Ministry of Higher Education and Research and EU-programme FEDER to the PIAnET CPER project is gratefully acknowledged. S.L., L.V.E. and R. M thank the Walloon Region, the FNRS, the IUAP VII and the ARC programs.

## REFERENCES

- Vande Velde G, Baekelandt V, Dresselaers T, Himmelreich U. Magnetic resonance imaging and spectroscopic methods for molecular imaging. *Q J Nucl Med Mol Imaging* 2009; 53: 565–585.
- Weissleder R, Ross BD, Rehemtulla A, Gambhir SS. *Molecular Imaging, Principles and Practice*. People's Medical Publishing House: USA, 2010.
- Hahn MA, Singh AK, Sharma P, Brown SC, Moudgil BM. Nanoparticles as contrast agents for in-vivo bioimaging: current status and future perspectives. *Anal Bioanal Chem* 2011; 399: 3–27.
- Aime S, Delli Castelli D, Geninatti C, Gianolio E, Terreno E. Pushing the sensitivity envelope of lanthanide-based magnetic resonance imaging (MRI) contrast agents for molecular imaging applications. *Acc Chem Res* 2009; 42: 822–831.
- Hainfeld JF, Slatkin DN, Focella TM, Smilowitz HM. Gold nanoparticles: a new X-ray contrast agent. *Br J Radiol* 2006; 79: 248–253.
- Debouttière PJ, Roux S, Vocanson F, Billotey C, Beuf O, Favre-Régouillon A, Lin Y, Pellet-Rostaing S, Lamartine R, Perriat P, Tillement O. Design of gold nanoparticles for magnetic resonance imaging. *Adv Funct Mater* 2006; 16: 2330–2339.
- Alric C, Taleb J, Le Duc G, Mandon C, Billotey C, Le Meur-Herland A, Brochard T, Vocanson V, Janier M, Perriat P, Roux S, Tillement O. Gadolinium chelate coated gold nanoparticles as contrast agents for both X-ray computed tomography and magnetic resonance imaging. *J Am Chem Soc* 2008; 130: 5908–5915.
- Arifin DR, Long CM, Gilad AA, Alric C, Roux S, Tillement O, Link TW, Arepally A, Bulte JW. Trimodal gadolinium-gold microcapsules containing pancreatic islet cells restore normoglycemia in diabetic mice and can be tracked by using US, CT, and positive-contrast MR imaging. *Radiology* 2011; 260: 790–798.
- Brust M, Fink J, Bethell D, Schiffrin DJ, Kiely C. Synthesis and reactions of functionalised gold nanoparticles. *J Chem Soc Chem Commun* 1995; 1655–1656.
- Sherry AD, Cacheris WP, Kuan KT. Stability constants for Gd<sup>3+</sup> binding to model DTPA-conjugates and DTPA-proteins: implications for their use as magnetic resonance contrast agents. *Magn Reson Med* 1988; 8: 180–190.
- Laurent S, Vander Elst L, Henoumont C, Muller RN. How to measure the transmetalation of a gadolinium complex. *Contrast Media Mol Imaging* 2010; 5: 305–308.
- Fournaise R, Petitfaux C. Etude de la formation des complexes en solution aqueuse – III. Nouvelle méthode d'affinement des constantes de stabilité des complexes et des autres paramètres des titrages protométriques. *Talanta* 1987; 34: 385–395.
- Geraldes CFGC, Urbano AM, Alpoim MC, Sherry AD, Kuan KT, Rajagopalan R, Maton F, Muller RN. Preparation, physico-chemical characterization, and relaxometry studies of various gadolinium(III)-DTPA-bis(amide) derivatives as potential magnetic resonance contrast agents. *Magn Reson Imaging* 1995; 13: 401–420.
- Martell AE, Smith RM. *Critical Stability Constants*. vol. 4. Plenum: New York, 1974.
- Leussing DL, Albert GS. The reactions of nickel(II) with 1,2-ethanedithiol. *J Am Chem Soc* 1960; 82: 4458–4461.
- Crisponi G, Diaz A, Nurchi VM, Pivetta T, Tapia Estevez MJ. Equilibrium study on Cd(II) and Zn(II) chelates of mercapto carboxylic acids. *Polyhedron* 2002; 21: 1319–1327.
- Bianchi A, Escuder B, Garcia-Espana E, Luis SV, Marcelino V, Miravet JF, Ramirez JA. Protonation tendencies of azaparcyclophanes. A thermodynamic and NMR Study. *J Chem Soc Perkin Trans 2* 1994; 10: 1253–1259.
- Kim HK, Jung HY, Park JA, Huh MI, Jung JC, Chang Y, Kim TJ. Gold nanoparticles coated with gadolinium-DTPA-bisamide conjugate of penicillamine (Au@GdL) as a T1-weighted blood pool contrast agent. *J Mater Chem* 2010; 20: 5411–5417.
- Kimura K, Takashima S, Ohshima S. Molecular approach to the surface potential estimate of thiolate-modified gold nanoparticles. *J Phys Chem B* 2002; 106: 7260–7266.
- Baranyai Z, Gianolio E, Ramalingam K, Swenson R, Ranganathan R, Brucher E, Aime S. The effects of intramolecular H-bond formation on the stability constant and water exchange rate of the Gd(III)-diethylenetriamine-N'-(3-amino-1, 1-propylenephosphonic)-N, N', "-tetracetate complex. *Contrast Media Mol Imaging* 2007; 2: 94–102.
- Garcés LJ, Castro CR, David C, Madurga S, Mas F, Pastor I, Puy J. Model-independent link between the macroscopic and microscopic descriptions of multidentate macromolecular binding; relationship between stepwise, intrinsic and microscopic equilibrium constants. *J Phys Chem B* 2009; 113: 15145–15155.
- Lacerda S, Campello MP, Marques F, Gano L, Kubicek V, Fouskova P, Toth E, Santos I. A novel tetraazamacrocyclic bearing a thiol pendant arm for labeling biomolecules with radiolanthanides. *Dalton Trans* 2009; 4509–4518.
- Sarka L, Burai L, Brucher E. The rates of the exchange reactions between [Gd(DTPA)]<sup>2-</sup> and the endogenous ions Cu<sup>2+</sup> and Zn<sup>2+</sup>: a kinetic model for the prediction of the *in vivo* stability of [Gd(DTPA)]<sup>2-</sup>, used as a contrast agent in magnetic resonance imaging. *Chem Eur J* 2000; 6: 719–724.
- Idée JM, Port M, Raynal I, Schaefer M, Le Greneur S, Corot C. Clinical and biological consequences of transmetalation induced by contrast agents for magnetic resonance imaging: a review. *Fundam Clin Pharmacol* 2006; 20: 563–576.
- Laurent S, Vander Elst L, Copoix F, Muller RN. Stability of MRI paramagnetic contrast media. A proton relaxometric protocol for transmetalation assessment. *Invest Radiol* 2001; 36: 115–122.
- Gu S, Kim HK, Lee GH, Kang BS, Chang Y, Kim TJ. Gd-complexes of 1,4,7,10-Tetraazacyclododecane-N,N',N'',N'''-1,4,7,10-tetraacetic acid (DOTA) conjugates of tranexamates as a new class of blood-pool magnetic resonance imaging contrast agents. *J Med Chem* 2011; 54: 143–152.
- Jaszberenyi Z, Banyai I, Brucher E, Kiraly R, Hideg K, Kalai T. Equilibrium and NMR studies on Gd(III), Y(III), Cu(II) and Zn(II) complexes of various DTPA-N,N-bis(amide) ligands. Kinetic stabilities of the gadolinium(III) complexes. *Dalton Trans* 2006; 1082–1091.
- Alderighi L, Gans P, Ienco A, Peters D, Sabatini A, Vacca A. Hyperquad simulation and speciation (HySS): a utility program for the investigation of equilibria involving soluble and partially soluble species. *Coord Chem Rev* 1999; 184: 311–318.

## SUPPORTING INFORMATION

Additional supporting information may be found in the online version of this article at the publisher's web site.