



HAL
open science

Crystallisation of cocoa butter particles with a new supercritical process

Jean-jacques Letourneau, S. Vigneau, P. Gonus, Jacques Fages

► **To cite this version:**

Jean-jacques Letourneau, S. Vigneau, P. Gonus, Jacques Fages. Crystallisation of cocoa butter particles with a new supercritical process. CHOPS 4 -4th International conference for conveying and handling of particulate solids, Mar 2003, Budapest, Hungary. p.2.1-2.6. hal-01782641

HAL Id: hal-01782641

<https://hal.science/hal-01782641v1>

Submitted on 25 Sep 2018

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

CRYSTALLISATION OF COCOA BUTTER PARTICLES WITH A NEW SUPERCRITICAL PROCESS

J.-J. Letourneau, S. Vigneau, P. Gonus* and J. Fages

"Chemical Engineering Laboratory for Particulate Solids"

UMR CNRS 2392

École des Mines d'Albi - 81013 Albi France

*Nestlé Product Technology Centre York, UK

Abstract – A new process using supercritical CO₂ has been developed to produce form V crystals of cocoa butter. In this process, solid cocoa butter is put in an autoclave in which supercritical carbon dioxide is then introduced. At high pressure, two liquid phases, one CO₂-rich and one cocoa butter-rich are formed. Both of them can be sent to a depressurisation nozzle leading to particle formation in an expansion vessel. Moreover, particles can also be formed in the first autoclave undergoing slower depressurisation. Both particle populations (upstream and downstream the nozzle) have been characterised using calorimetric method (DSC) and environmental scanning electron microscopy (ESEM). The polymorphism of the particles produced as well as their size and morphology show that they are potentially usable in the tempering step of the manufacturing process of chocolate.

1. INTRODUCTION

1.1 Polymorphism of cocoa butter and chocolate tempering

Cocoa butter, the fat of chocolate, is responsible for the pleasant “melt in the mouth” sensation given by chocolate. It is a complex mixture of triacylglycerol (TAGs), which melting points are in the “good” range to give this feeling. [1]

The most abundant are monounsaturated TAGs, the unsaturated fatty acid (very often oleic acid) being in the 2-position. 1-palmitoyl-2-oleyl-3-stearoylglycerol (POS) ; P-O-P and S-O-S account for 36-38 %, 14-16 % and 23-28 % respectively of the total TAGs. It is these TAGs which are mainly responsible for the behaviour of chocolate when undergoing crystallisation [2].

There are six different ways for these TAGs to arrange themselves when they crystallise. Six different polymorphs noted I – the less stable with the lowest melting point 290 K (17°C) – to VI – the most stable with the highest melting point 308 K (35°C) – can be obtained. The relative amount of these six polymorphs will condition several features of the end product. If the wrong type of fat is present the chocolate may exhibit a white powdery surface called fat bloom which is to be avoided because of its unpleasant appearance. The most desirable form is known as form V (or β_2) having a melting temperature of 305–307 K (32–34°C). The transfer to the even more stable form VI is not desirable since it might lead to fat bloom as do the less stable forms.


The processing conditions determine which polymorph is formed. To obtain predominantly form V a pre-crystallisation step also called tempering has been introduced in the chocolate manufacturing process. It is aimed at the formation of form V seed crystals which in turn will force

the bulk of the remaining fat to crystallise in this stable form. Two main ways are used: (i) starting with hot liquid chocolate 318–323 K (45–50°C) a succession of cooling to 300 K (27°C) in order to form both stable and unstable crystals followed by re-heating to 303–305 K (30–32°C) to melt only less stable crystals will lead to some form V crystals which, in turn, will seed the mass of chocolate and (ii) seeding the mass of untempered chocolate by finely divided form V crystals of cocoa butter.

1.2 Crystallisation with supercritical processes

Supercritical fluid (SCF) technology presents a new and interesting route for particle formation, which avoids most of the drawbacks of the traditional methods of milling/crushing or liquid crystallisation. Supercritical processes are known to give micro- or even nano-particles with narrow size distribution, and may allow the control of crystal polymorphism. In addition, several other advantages inherent to these processes must be emphasised: they are single-step processes with simplified downstream processing and they are environmentally desirable since they avoid the use of organic solvents. Moreover they allow the processing of thermolabile molecules and give high purity products [3].

Although most of the applications of supercritical particle formation are known in the pharmaceutical industry, some examples can be found with foodstuff. Cocoa butter a relatively high value product has been successfully micronised using the PGSS (Particles from Gas-Saturated Solution) process.

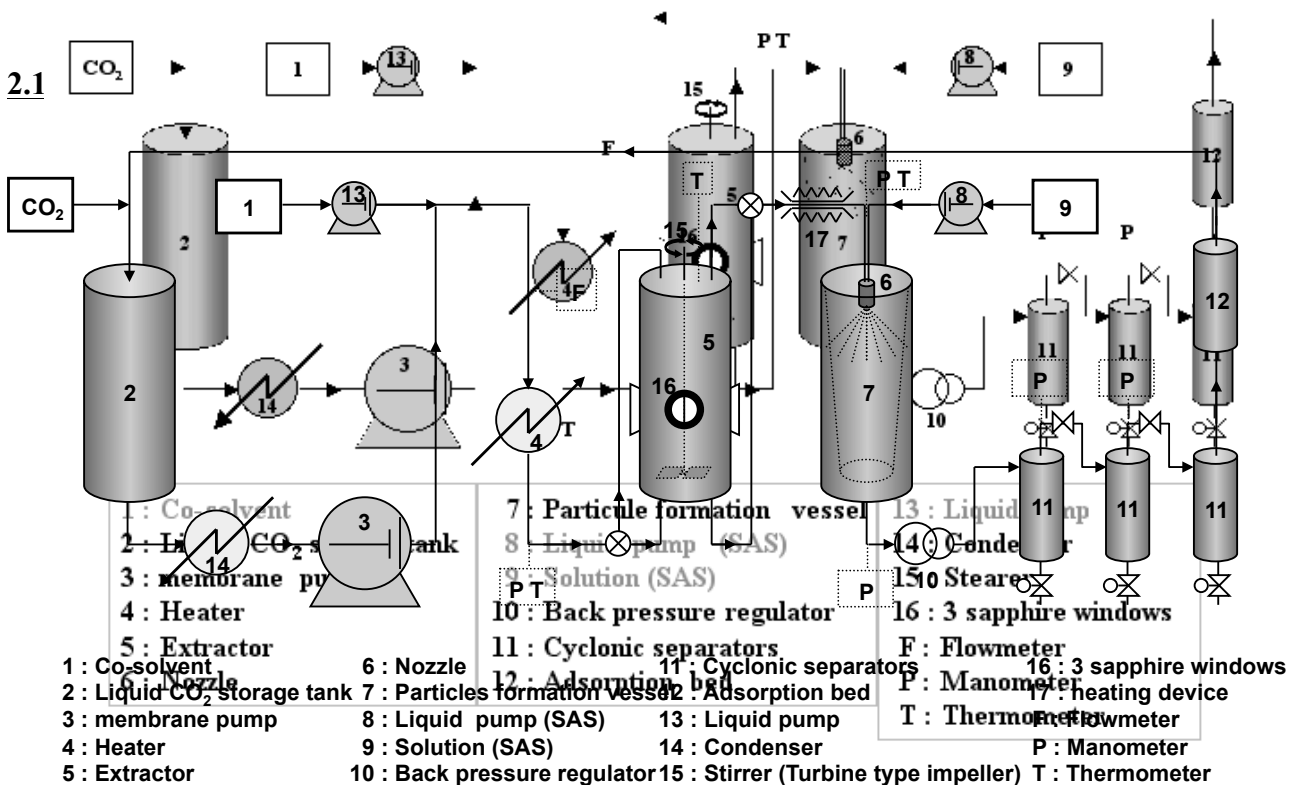

The experiments were carried out in a versatile pilot plant (Separex, France). A schematic diagram of the apparatus is shown in figure 1. Carbon dioxide is cooled and stored in a liquid CO₂ storage tank (2). It can be circulated at a maximum flow of 25 kg.hr⁻¹ by a membrane pump (Lewa, Germany) (3). Compressed CO₂ passes then through a heat exchanger (4) and becomes supercritical. Some of the devices (1, 8, 9, 13) shown in figure 1 are used for other experiments such as SAS or RESS with co-solvent.

The vessel (5) (PARR Instrument, USA) is equipped with 3 sapphire windows (16), a magnetic stirrer (15) with a maximum torque of 1.8 Nm and a flexible mantle heater.

The flow coming out this vessel is sprayed into the expansion vessel (7) by means of a nozzle (6) (Spraying System, France). The powder formed is collected in a porous bag made of PTFE fibres. Then, CO₂ is depressurised (10) and can either be directed to the vent or purified and recycled.

2.2 Cocoa butter particle generation

Pieces of solid cocoa butter are loaded in the vessel (5) equipped with a stirrer and this vessel is filled with CO₂. Then, the operating temperature and the stirrer speed are fixed by the controllers. Further addition of CO₂ allows reaching the operating pressure. The mixture thus obtained is stirred during a long enough period of time in order to reach the thermodynamic equilibrium. In particular if two liquid phases are present, each of them is assumed to be saturated.

The second vessel (7) is then filled with CO₂ until reaching the second operating pressure. This is the expansion pressure at which the mixture is placed downstream of the nozzle. This pressure is fixed during all the experiment with a back-pressure regulator (10).

The temperature of the CO₂ upstream the stirred vessel is controlled by the heating device (4) and fixed to be the same as the temperature of the mixture in the stirred vessel.

During the experiments the valve between the two vessels is open. The saturated mixture sprayed into the expansion vessel via the nozzle, is subjected to a sudden drop in pressure, resulting in supersaturated conditions and the crystallisation of the cocoa butter. This powder is collected in the bag inside the second vessel. This process is known as a RESS process (Rapid Expansion of Supercritical Solutions).

Two major types of experiments have been achieved:

- In the first one, the first vessel is let to slowly depressurise during its emptying through the nozzle. Therefore, particles of cocoa butter can also be formed in this vessel.
- In the second, the membrane pump (3) feeds the vessel with CO₂ in order to compensate the emptying via the nozzle and to maintain a constant pressure.

Another refinement in the classification of types of experiments depends on the initial load of cocoa butter. For small amounts, the mixture appears in a homogenous single phase. On the other hand, when the initial amount increases, two phases are present.

If the temperature is too low, the solid cocoa butter formed this second phase, but with higher temperatures two fluid phases are in equilibrium: one is rich in CO₂ and the other is rich in cocoa butter. Kokot *et al.* [5] showed that at 313 K and 20 MPa, the mass fractions of CO₂ for these two phases are 0.44 and 0.98. When working with two fluid phases and without stirring, the results of the experiments depend on the position of the outlet pipe of the first vessel: top or bottom. If the fluid is extracted from the top of the vessel, the cocoa butter powder is produced from the richest phase in CO₂. Conversely it is the cocoa butter rich phase which is extracted from the bottom. If the mixture is homogenised by agitation these two phases are mixed and the resulting fluid appears (as seen through the windows) to be homogenous just like an emulsion.

The drop in pressure undergone by the mixture in the nozzle, leads also the temperature to fall and crystals of CO₂ may appear (CO₂ triple point: T = 216.6 K P = 0.52 MPa). To prevent this solid CO₂ formation, the pressure P₇ in the expansion vessel must be kept beyond the triple point pressure. But this does not always prevent the CO₂ liquefaction if the temperature upstream the nozzle is not high enough (the final temperature of pure CO₂ at T = 333 K submit to an isenthalpic depressurization from P = 10 MPa to P = 1 MPa is T = 233 K, a point on the boundary of the liquid-vapor region). The presence of two phases – liquid and gas – around the particles in formation could change the growth of the crystals and therefore their final morphology. The heating device (17) is used to prevent the temperature T₇ in the expansion vessel to be lower than the dew temperature of pure CO₂ at P₇.

The flowrate of CO₂ is adapted to fit with the operating conditions. It mainly depends on the characteristics of the nozzle and on the pressure difference P₅ - P₇ between the two vessels. A typical flowrate value for the experiences listed in the table 1 is about 20 kg.hr⁻¹.

2.3 Powder characterisation

Differential scanning calorimetry (DSC) has been used to characterise the samples is a DSC-7 Perkin-Elmer. The DSC patterns of the samples (2-5 mg) were obtained between 283 K to 323 K at a heating rate of 5 K.min⁻¹ in a N₂ gas stream.

The picture presented in figures 3 and 4 have been made with an Environmental Scanning Electron Microscope (XL30 ESEM FEG, FEI Philips, Netherlands).

3. RESULTS AND DISCUSSION

3.1 Particle formation experiments

The first series of experiments (E-I) was done with small amounts of cocoa butter (single-phase system) and with continuous feeding in CO₂. The second series (E-II) was done without feeding and top extraction: particles were collected in both vessels. The third series (E-III) was done without feeding and bottom extraction: particles were collected in both vessels. The fourth series (E-IV) was done with larger amounts of cocoa butter, continuous feeding and bottom extraction. The fifth and last series of experiments (E-V) was done with larger amounts of cocoa butter and homogeneous mixing.

Table 1. Experimental operating conditions

Exp. #	Series	Diam (mm)	M ₀ (g)	V ₅ (cm ³)	P ₅ (MPa)	T ₅ (K)	P ₇ (MPa)	T ₇ (K)	Duration (min)
1	E-I	0.23	20.8	2000	20	313	0.6	288	22
2	E-I	0.23	30.6	2000	25	373	0.6	288	28
3	E-I	0.41	18.6	2000	20	318	1	288	22
4	E-I	0.41	36	2000	20	323	0.1	288	21
5	E-I	0.41	20.1	2000	30	313	0.9	288	20
6	E-II	0.41	20.6	2000	25	303	0.1	291	10
7	E-II	1.5	20.2	2000	30	303	0.1	293	6
8	E-III	0.41	19.9	2000	30	313	0.1	289	4
9	E-III	1.5	102.3	2000	31	298	0.1	292	3
10	E-IV	0.23	99.7	2000	20	293	0.7	291	7
11	E-IV	0.23	106.4	2000	27	305	0.4	288	24
12	E-IV	0.41	100.6	2000	20	313	0.2	288	14
13	E-IV	0.41	94.4	2000	32	313	0.3	288	15
14	E-V	0.23	128	1200	20	303	4	283	5
15	E-V	0.23	135	1200	25	308	2	283	5

Diam.: diameter of the nozzle orifice; M₀: initial mass of cocoa butter; V₅, P₅, T₅: respectively volume, pressure and temperature of the tank (5); P₇, T₇: respectively pressure and temperature of the tank (7);

In figure 2 are shown the DSC patterns for the original cocoa butter and for experiments 5 and 15. Original cocoa butter shows a peak at T = 307.1 K, an end-set point at T = 309.6 K and a melting enthalpy of $\Delta h^{\text{fus}} = 131 \text{ J.g}^{-1}$, which are characteristics values for form VI crystals.

The powder obtained in experiment 15 was collected in the bag of the expansion vessel. Its characteristics are: T_{peak} = 304 K, T_{endset} = 306.3 K and $\Delta h^{\text{fus}} = 120.3 \text{ J.g}^{-1}$. This form V powder was white, light, with regular individual particles and was free-flowing. Nearly all experiments achieved with the following conditions: nozzle orifice diameter = 230 μm, 298 ≤ T₅ ≤ 308 K, P₅ ≥ 20 MPa and 0.5 ≤ P₇ ≤ 4 MPa led to the same kind of form V powder collected in the expansion vessel (7). A typical example of this kind of particle is shown on figure 3. It is made of an agglomeration of smaller particles.

The powder obtained in experiment 5 was collected in the vessel (5) and has the following characteristics: $T_{\text{peak}} = 300.5 \text{ K}$, $T_{\text{endset}} = 302.5 \text{ K}$ for the first peak and: $T_{\text{peak}} = 303.7 \text{ K}$, $T_{\text{endset}} = 305.0 \text{ K}$ for the second peak. All the particles obtained in this vessel are made of a mixture of both form IV and V. The faster the drop in pressure in this vessel, the larger the quantity of form V powder obtained. A typical example of this kind of particle is shown in figure 4. This powder is generally white, extremely light and sometimes pieces of original yellow cocoa butter can be found among the particles.

Figure 2: Typical DSC curves

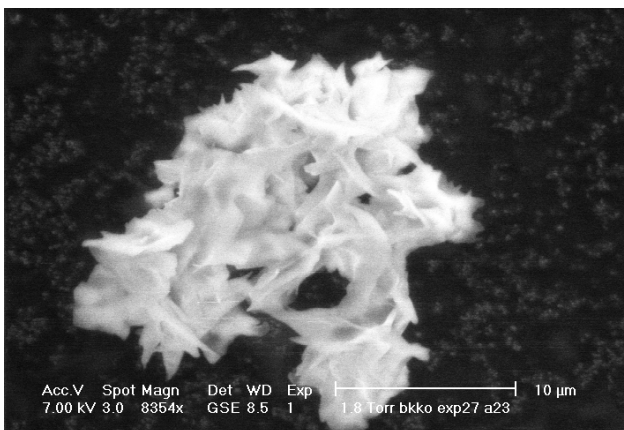


Figure 3: ESEM picture of a cocoa butter particle obtained with Exp # 14.

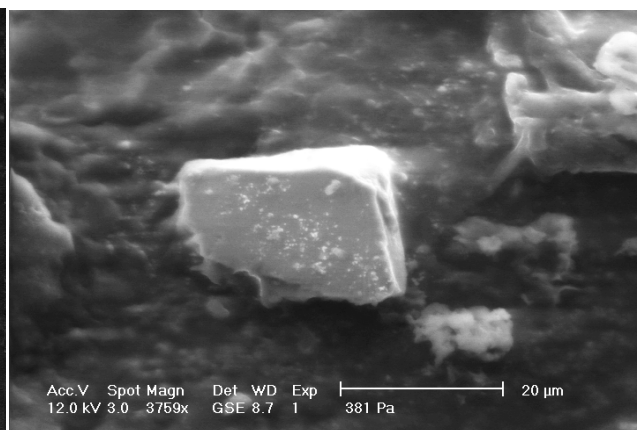


Figure 4: ESEM picture of a cocoa butter particle obtained with Exp # 5.

3.2 Seeding of chocolate

Chocolate tempering experiments were carried out by seeding with various type of cocoa butter powder. The degree of pre-crystallisation (temper) was measured using a computerised tempermeter (Exotherm 7400 from Systech Analytics). This measurement is basically a cooling curve where the change in temperature is measured against the time. The chocolate sample is taken at processing

temperature in a special container and placed in the instrument cell at 281 K (8°C). In a typical tempering curve, the exothermic process of crystallisation generates an inflexion point. The slope at this point is used to determine if the chocolate is under-, well- or over-tempered. Usually a well-tempered curve shows an horizontal plateau. More details on tempering curve measurements can be found in Bolliger *et al.* [6].

The process of cocoa butter seeding is usually carried out at 303 K (30°C) where a mass fraction of 0.5% to 2% of ordinary cocoa butter seeds is mixed with the melted chocolate.

The cocoa butter powder obtained by supercritical process was able to seed using the following conditions.

At 306 K (33°C) and above, the seeding produced an under-tempered chocolate; at 304 K (31°C) and below, the chocolate was quickly over-tempered. However at 305 K (32°C), good tempering conditions were obtained with less than 0.3% of cocoa butter seeds. This is at least 2°C higher than common seeding and several degrees higher than most industrial temperer. Therefore, the chocolate is very much thinner.

The powder samples described in series E-I and E-IV (obtained with the smallest nozzle) gave the best results. The seeding was carried out at 305 K (32°C) with a mass fraction of 0.1-0.2% and produced a well-tempered chocolate. At this high temperature, the stirrer velocity is a critical point as an excess of mechanical energy could melt the seeds.

4. PERSPECTIVES AND CONCLUSION

The best cocoa powders in terms of appearance, DSC, reproducibility and shelf-stability are those of the E-V series. They have not been tested yet to seed chocolate and this will be part of a future work.

High shear stresses are known to favour the most stable forms of the cocoa butter. The same phenomenon is probably also appearing in the supercritical generation of cocoa butter particles: when the particles are generated in the expansion vessel with a huge drop in pressure through a small nozzle, they are exclusively made of form V – when generated in the first vessel with a slow drop in pressure form IV is present and even predominant. This is a track for further studies.

A major interest in using this new process [7] is the value of the temperature at which seeding can be done with the cocoa butter particles "supercritically" generated. At 305 K the chocolate is less viscous which is advantageous in term of flowability and energy consumption. An additional advantage lies in the fact that the time needed to obtain a well-tempered chocolate is shorter (about 5 minutes). Moreover, the overall quantity of seeds to temper the chocolate is very small. Therefore, a scaling-up of this process to an industrial scale appears feasible.

5. REFERENCES

1. S.T.Beckett, *The science of chocolate*, RSC paperbacks, 2000.
2. M. Lipp and E. Anklam, Review of cocoa butter and alternative fats for use in chocolate. Part A. Compositional data, *Food chem.*,62, pp.73-97, 1998.
3. J. Fages, H. Lochard, E. Rodier, J.-J. Letourneau and M. Sauceau, La Génération de Solides Divisés par Fluides Supercritiques, *Can. J. Chem. Eng. In press*, 2003.
4. Z. Knez and E Weidner, Precipitation of solid with dense gases, In : *High pressure process technology : fundamentals and applications*, A. Bertucco and G Vetter eds., Elsevier, pp 587-611, 2001
5. K. Kokot, Z. Knez and D. Bauman, S-L-G (Solid-Liquid-Gas) phase transition of cocoa butter in supercritical CO₂, *Acta Alimentaria* **28**, pp. 197-208, 1999.
6. S.Bolliger, B.Breitschuh, M.Stranzinger, T.Wagner and E.J.Windhab, *J. Food Eng.* **35**, pp 281-297, 1998
7. J. Fages and J.-J. Letourneau, French patent pending, 2002