



HAL
open science

Characterization of Barley Straw, Hemp Shiv and Corn Cob as Resources for Bioaggregate Based Building Materials

Aurélie Laborel-Préneron, Camille Magniont, Jean-Emmanuel Aubert

► **To cite this version:**

Aurélie Laborel-Préneron, Camille Magniont, Jean-Emmanuel Aubert. Characterization of Barley Straw, Hemp Shiv and Corn Cob as Resources for Bioaggregate Based Building Materials. *Waste and Biomass Valorization*, 2018, 9 (7), pp.1095 - 1112. 10.1007/s12649-017-9895-z . hal-01876843

HAL Id: hal-01876843

<https://hal.science/hal-01876843>

Submitted on 18 Sep 2018

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

1 **Characterization of barley straw, hemp shiv and corn cob as resources for**
2 **bioaggregate based building materials**

3

4 Aurélie Laborel-Préneron^a, Camille Magniont^a, Jean-Emmanuel Aubert^a

5 ^a *LMDC, Université de Toulouse, INSA/UPS Génie Civil, 135 Avenue de Rangueil, 31077*
6 *Toulouse cedex 04 France.*

7

8 *Corresponding author: Aurélie Laborel-Préneron

9 Tel. +33 (0)5 61 55 99 26 Fax: 0033 (0)5 61 55 99 49;

10 e-mail: alaborel@insa-toulouse.fr

11

12 **ABSTRACT**

13 Expanding the use of low-environmental impact materials in the field of building materials is a
14 major aim in a context of sustainable development. These alternative materials should be
15 non-polluting, eventually recycled, and locally available. Bioresources are already used in
16 some building materials but few studies have investigated their relevance in such
17 applications. The aim of this paper is to evaluate the suitability of three kinds of vegetal
18 aggregates: barley straw, hemp shiv and corn cob. The availability of these bioresources,
19 extracted from a French database, is discussed, as are their physical properties and
20 chemical compositions. Their microstructure is described with SEM images and their particle
21 size distributions are provided through image analysis. Sorption-desorption isotherms are
22 measured by a Dynamic Vapour Sorption system. Bulk density, thermal conductivity and
23 water absorption are also quantified. The results highlight a tubular structure for the three
24 different aggregates, with low bulk density and thermal conductivity (0.044, 0.051 and 0.096
25 $W.m^{-1}.K^{-1}$ respectively for straw, hemp shiv and corn cob) and high water absorption,
26 especially for barley straw and hemp shiv (414 and 380% vs. 123% for corn cob). Their
27 hygric regulation capacity is also sufficiently good, with a water sorption of between 20 and
28 26% at 95% of relative humidity. These plant aggregates could therefore be used as
29 additions in an earth matrix, or a hydraulic, pozzolanic, air lime or gypsum binder, or just as
30 loose-fill insulation material. However, future research should focus on their resistance to fire
31 and bacterial growth to validate this approach.

32

33 **Keywords:** Barley straw, hemp shiv, corn cob, bio-based building material, availability,
34 properties

35

36 1. INTRODUCTION

37 The impacts of buildings on environment, and especially on energy consumption and CO₂
38 emissions have now become priority issues. Energy use in buildings generates about 40% of
39 the EU's total final energy consumption and 36% of its CO₂ emissions [1]. Innovation or
40 changes are thus necessary to decrease buildings' environmental impact and improve their
41 energy efficiency. Currently, in France, a huge proportion of non-renewable materials is used
42 in the construction industry and large amounts of waste are produced (around 50 million tons
43 per year, while municipal solid waste is around 30 million tons per year [2]).

44 On the way to a sustainable future, eco-friendly building materials could be part of the
45 solution. These materials would allow consumption and pollution to be reduced during the
46 production process and also during their whole service life and their end-of-life. In that
47 context, bio-based building materials present the advantage of using plant resources that
48 have absorbed CO₂ through photosynthesis and can thus reduce the material's
49 environmental impact by sequestering CO₂ for at least the life-time of the construction [3].
50 Bio-sourced materials and the building sector have been identified by the French Ministry of
51 Ecology, Sustainable Development and Energy (Commissioner-General for Sustainable
52 Development) as one of the 18 "green" sectors with a high potential for economic
53 development in the future. In order to produce these low carbon materials, renewable
54 resources, such as by-products from agriculture or forests, are needed. An example that is
55 being increasingly studied is a bio-based earth material. Unfired earth bricks are fibred with
56 distinct renewable resources such as kenaf fibre [4], straw [5], wood chips [6] or wool fibre
57 [7]. Plant concretes, which combine bioaggregates with a pozzolanic, lime-based or cement
58 matrix, are also a good alternative. Numerous studies on hemp concrete currently exist [8-
59 11] and there are also some concerning sunflower [12] or lavender [13] concrete. Although
60 bio-resources are renewable, they also need to be cultivated at locations close to where they
61 are implemented so as to avoid unnecessary transportation and its related environmental
62 impacts. For that reason, the present paper focuses on estimating the potential availability of
63 such resources in the case of France, where by-products and the availability of agricultural
64 land are increasingly being studied, especially with a view to the use of bio-fuels [14-16].
65 However, these studies provide information about quantities of available, still-unused by-
66 products which could be employed as building materials. A similar study has already been
67 carried out by Palumbo et al. [17] for insulating materials. Their study focused on the main
68 resources available in Europe and especially in Spain, i.e. cereals and sunflower. Biomass is
69 more and more in demand. In the past, it was already used but population growth
70 engendered an increase in food needs. Studies are now being conducted to avoid biomass
71 usage conflicts between priority sectors and others. The former concern human
72 consumption, including animal feed and litter, whereas the latter are related to industry

73 (biomaterials, bio-based chemistry) and energy, which are considered as lower priority by
74 France Agrimer [18]. This study will focus only on plant-sourced biomass.

75 Plant particle characteristics, which are very specific to the raw material, are studied and
76 compared in the present paper. These characteristics have to be taken into account in the
77 development and the characterization of further composite materials. Three plant aggregates
78 were studied in this work because they were readily available and presented important
79 morphological differences: barley straw, hemp shiv and corn cob. Straw is currently one of
80 the most commonly studied plant aggregates, and is the subject of one third of the 50
81 references reviewed by Laborel-Préneron et al. [19]. This resource, very common in the plant
82 world, is also present in our cultural heritage [20], [21]. It can come from wheat [22-24],
83 barley [22], [25], oats [26] or other cereals. Hemp shiv constitutes a resource that has
84 received considerable attention in France, which is the greatest producer of hemp in Europe
85 with more than 50% of the total European production [27]. This plant aggregate is especially
86 studied for use in hemp concrete [28], [29] but also as a bio-composite material with earth
87 [30], [31]. Corn cob is an original resource that has been studied only once with an earth
88 matrix, but not crushed [32]. It was studied by Verdier et al. in a pozzolanic matrix [33], and
89 corn pith, which is softer, was studied by Palumbo as an insulating material in an alginate
90 matrix [34].

91 The use of bio-based aggregates in building materials is becoming increasingly widespread.
92 It is worth noting that various plant aggregates are available in the world and could be used
93 for building construction. However at the present time, no international standardized method
94 exists for characterizing such materials, as it already exists for mineral aggregates. The new
95 standard could define testing protocols for the characterization of bio-aggregates and also
96 the restrictions applying to each application in building materials. This lack of recognized
97 procedures led the RILEM BBM Technical Committee to work on recommendations
98 concerning protocols for bio-aggregate characterization, mainly on hemp shiv [35].

99 Applying these recommendations to other plant aggregates is a way to check the validity of
100 the method. The objective of this study is thus to characterize and observe the differences of
101 three available agro-resources by following the RILEM recommendations in terms of bulk
102 density, thermal conductivity, water absorption and particle size analysis. Complementary
103 characteristics proposed by other authors are also studied: availability in France, microscopic
104 description, chemical composition and sorption-desorption capacity. This whole methodology
105 could allow the differences between the characteristics of these three plant particles to be
106 highlighted and their potential for future applications in building materials to be assessed.

107

108 2. MATERIALS AND METHODS

109 2.1. Materials

110 2.1.1. *Barley straw*

111 Straw is an agricultural by-product and is the part of cereal stems rejected during the harvest.
112 Barley is harvested once or twice a year. It is the third most cultivated cereal in France with
113 10 million tons per year [18]. The straw studied here (Fig.1), already chopped, was supplied
114 by the CalyClay company (Drôme, France), which is specialized in services for straw and
115 earth construction.


116 2.1.2. *Hemp shiv*

117 France was the first producer of hemp in 2013 [36]. Hemp shiv is the by-product of the hemp
118 defibration process and corresponds to the lignin-rich part of the stem (Fig.1). It was provided
119 by the Agrofibre company in Cazères (Haute-Garonne, France).

120 2.1.3. *Corn cob*

121 Maize is the second most cultivated cereal in France, with around 15 million tons per year
122 [18]. Corn cob is the central part of the ear of maize, cleared of grain and crushed. The
123 “woody” part (in red in Fig.1), which is also the hardest part, was studied here. This corn cob,
124 already calibrated, was provided by the Eurocob company in Maubourguet (Hautes-
125 Pyrénées, France).

126

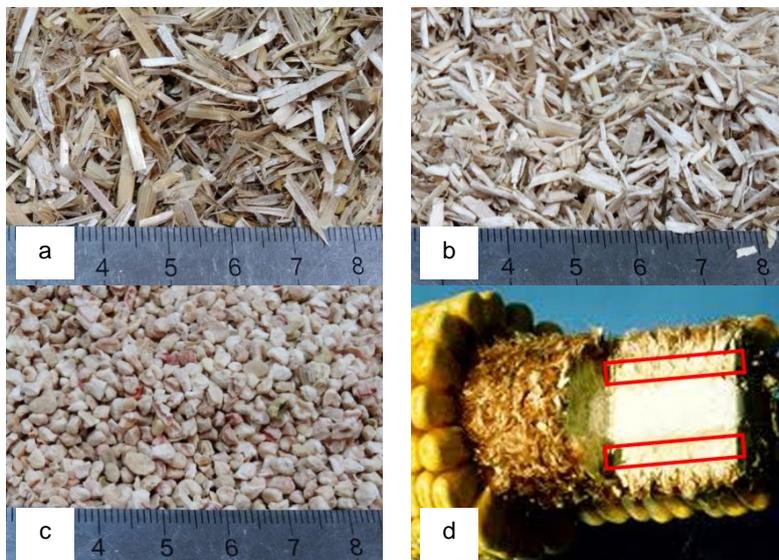

127 **Fig.1** Raw materials (a) Barley straw, (b) Hemp shiv, (c) Corn cob and (d) Part of corn
128 studied (in red)

129 2.2. Availability of agricultural and forestry by-products

130 The availability of resources was estimated for the case of metropolitan France and
131 specifically for biomass from agriculture, the agri-food sector, industrial crops and forestry
132 residues. Most data providing both the yearly total and the available production of crop by-
133 products come from a national authority, France Agrimer [18], which monitors products and
134 biomass from agriculture and the sea. The data presented in this study are from 2015 and

135 some values were completed by data from 2013-2014 in Agreste [37], provided by the
136 French *Ministère de l'Agriculture, de l'Agroalimentaire et de la Forêt*. In these two references,
137 data were collected from various economic bodies such as Ademe (*Agence de*
138 *l'Environnement et de la Maîtrise de l'Energie*), IGN (*Institut National de l'Information*
139 *Géographique et Forestière*) and the FAO (*Food and Agriculture Organization of the United*
140 *Nations*). Nevertheless, the collected information should be interpreted cautiously, as a
141 resource may not have been fully counted.

142 Some data, specifically for industrial crops, were expressed only as quantity produced, and
143 were therefore converted into quantity available by applying the unused biomass factor found
144 in Jölili and Giljum [38]. Furthermore, data corresponding to forestry biomass were given by
145 volume per year (Mm^3/y). In order to be compared with the other resources, volume was
146 converted into mass assuming a density of $0.88 t/m^3$, which is an average for various wood
147 species from an FCBA memento [39]. No recent data were available concerning fruit
148 production, except for those for wine and cider production. Agri-food industry by-products will
149 be thus slightly undervalued.


150

151 Twenty-four distinct resources were documented in these two references (France Agrimer
152 and Agreste), such as soft wheat, sunflower and beetroot. It was decided to group them into
153 5 families: cereals, oilseed crops, industrial crops, agri-food industry residues and wood
154 residues.

155 The method for determining the available by-products (Ba) was based on the following
156 equation 1, greatly inspired by the work of Palumbo et al. [17]

$$Ba = Bt - Bn - Bu \quad (1)$$

157 where Bt is the total by-products (Mt/y), Bn is the non-harvestable by-products (Mt/y)
158 (necessary to maintain soil fertility or inaccessible) and Bu corresponds to by-products
159 allocated for other uses (Mt/y) such as litter, animal feed or energy (only in the case of
160 wood). All quantities of by-products were expressed by mass (dry basis) over one year and
161 they were determined from areas and farm yield. This equation is recapitulated by Fig.2.

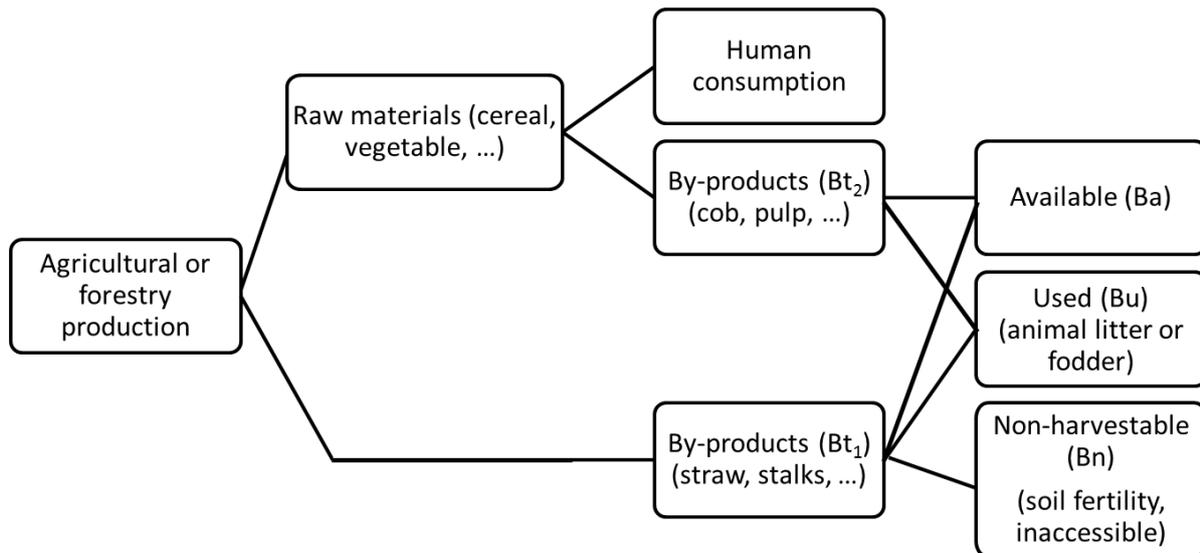

162

163 **Fig.2** Recapitulative scheme of utilization of by-products

164 For example, for oleaginous plants, it was considered that the minimum return to the soil to
 165 maintain agronomic potential was 50% of the straw produced [18].

166

167 **2.3. Physical properties of plant aggregates**

168 Most of the physical plant aggregate characterization tests were based on a current work of
 169 the RILEM TC 236-BBM because there is no standardized method for this kind of material.
 170 To evaluate the validity of the results and analyse the dispersion of the results, these
 171 protocols recommend calculating a coefficient of variation. This coefficient corresponds to the
 172 ratio between the standard deviation and the mean value. The mean value is considered to
 173 be representative if the coefficient is lower than 5%. The methods are explained in the
 174 following sections.

175

176 **2.3.1. Microscopic description (SEM images)**

177 Porous structure and morphology were analysed visually with a JEOL - JSM-6380 LV
 178 Scanning Electron Microscope (SEM). The particles were glued onto a metallic support and
 179 then covered with a thin layer of evaporated gold before observation. These microstructural
 180 investigations were carried out with a 15 kV accelerating voltage in high vacuum mode.


181

182 **2.3.2. Particle size analysis**

183 A particle size analysis was performed by image analysis using ImageJ software. This
 184 increasingly used method [40-42] is particularly interesting in the case of non-spherical
 185 particles. Size distribution and morphology (width and length) were determined using this
 186 method whereas traditional mechanical sieving analysis would have given only the width.
 187 However, this method is only achievable for small quantities of particles.

188 First, the particles were sieved at 500 µm to remove dust. The plant aggregates were then
 189 homogenized before being distributed into small boxes. The particles were scanned on a
 190 black background in order to obtain better contrast for the ImageJ analysis (Fig.3). All the
 191 particles were then grouped into a single table to plot representative curves. In total, more
 192 than 7000 particles were analysed for each type of plant aggregate which corresponds to a
 193 mass of 6.7 g of straw, 13.6 g of hemp shiv or 71.0 g of corn cob. This is more than the mass
 194 recommended by the RILEM TC 236-BBM, of between 3 and 6 g, or the minimum number of
 195 1000 particles suggested by [43]. Sampling quality is a key point for the representativeness
 196 of the results.

197

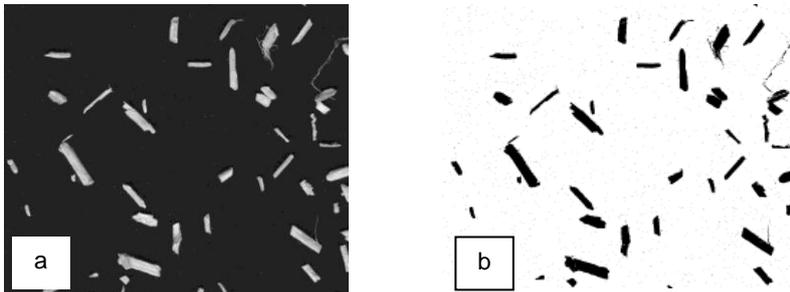

198 **Fig.3** Particle image processing of straw: (a) Scan in shades of grey, (b) Image processing

199 This analysis gave the geometrical parameters of the particles: the major and minor axis
 200 lengths (Major and Minor respectively), and the Equivalent Area Diameter (EAD), based on a
 201 particle of circular cross section and calculated with equation 2:

$$EAD = \sqrt{\frac{4 * A}{\pi}} \quad (2)$$

202 with A the cross sectional area of the particle (m²). It also gave the aspect ratio (AR) which is
 203 the length to width ratio, or Major to Minor ratio. If the value is close to 1, the particle is
 204 almost circular or square; the more AR differs from 1, the more elongated is the particle.

205

206 2.3.3. Bulk density

207 Three specimens of each plant aggregate were dried at 60°C until the weight became
 208 constant (weight variation of less than 0.1% between two weighings 24 h apart). Each
 209 specimen was put in a cylindrical mould 12 cm in diameter and 24 cm high. The mould
 210 dimensions were chosen in accordance with the RILEM work. The RILEM TC observed that
 211 the mould size used to measure bulk density had very little effect on the density as long as
 212 the height was at least twice the diameter and the diameter was at least 10 cm (big enough
 213 compared to the particle size). The quantity of material was selected by a quartering
 214 procedure and adjusted to be half the volume of the mould. The mould was then upended 10
 215 times before the final level was marked with a cardboard disk. The volume occupied by the

216 particles was measured from the weight of the corresponding volume of water and the bulk
217 density (ρ_b , kg.m⁻³) was calculated using equation 3:

$$\rho_b = \frac{m_d}{m_w} \times \rho_w \quad (3)$$

218 where m_d is the mass of dry particles (kg), m_w is the mass of water (kg) and ρ_w is the density
219 of water (1000 kg.m⁻³).

220 The bulk density of a given type of plant aggregate was taken as the average value
221 measured on three samples.

222

223 2.3.4. *Thermal conductivity*

224 Three specimens of each plant aggregate were dried at 60°C until the weight became
225 constant (weight variation less than 0.1% between two weighings 24 h apart). The particles
226 were put in a PVC box of dimensions 15x15x5 cm³, thermal conductivity 0.11934 W.m⁻¹.K⁻¹
227 and thickness 1.6 mm. According to the recommendations of the RILEM TC 236-BBM, the
228 dry density of the sample for thermal conductivity measurement was checked and adjusted
229 (by shaking) to the same value measured during the bulk density test. For this last test, the
230 procedure recommends upending the cylindrical mold ten times. The measurements were
231 made with a hot plate apparatus (λ -meter EP 500) and were performed at 25°C. The
232 specimen was located between the two plates of the apparatus, one hot and the other one
233 cold, with a temperature difference of $\Delta T=10$ K. A steady state was assumed to have been
234 reached when the change in conductivity was less than 1% in 60 minutes. The apparent
235 thermal conductivity of the plant aggregates within the PVC box (λ_{app} in W.m⁻¹.K⁻¹) was
236 calculated at the steady state with the following equation:

$$\lambda_{app} = \frac{Q \cdot e_t}{\Delta T \cdot S} \quad (4)$$

237 where Q is the heat input (W), e_t the total thickness (m) and S the cross section of the
238 specimen (m²). Knowing the dimensions and thermal conductivity of the PVC box, the
239 thermal conductivities of the plant aggregates were then deduced. A transfer by conductivity
240 through the plant aggregates and the box was assumed.

241 The specimens were weighed at the end of the test to measure the water uptake during the
242 measurement.

243

244 2.3.5. *Water absorption*

245 Water absorption during 1 minute, 15 minutes, 4 hours and 48 hours was measured on 3
246 specimens of each of the 3 plant aggregates. Each sample was dried at 60°C until the weight
247 became constant (weight variation less than 0.1% between two weighings 24h apart).
248 Specimens were put into permeable nets for which the water absorption was negligible. Their

249 mass, of 25 g for straw, 20 g for hemp shiv and 50 g for corn cob, depended on the available
250 volume of the nets. It is assumed that representativeness was ensured by careful mixing and
251 quartering the particles. After water immersion, the samples were drained for 1 minute in
252 their nets with a salad spinner and then weighed to determine their water absorption (%)
253 according to the following equation:

$$w(t) = \frac{m(t) - m_0}{m_0} \times 100 \quad (5)$$

254 where $m(t)$ is the wet mass after spinning (kg) and m_0 is the dry mass (kg).
255

256 2.4. Chemical characterization

257 Before the tests, samples were crushed to a grain size of less than 1 mm and dried at 105°C
258 for at least 12 h. The main chemical compounds were measured by the Eurofins company
259 using the Van Soest method, according to standard NF V18-122 [44]. This test provides 3
260 results: NDF (Neutral Detergent Fibre), corresponding to the total fibre; ADF (Acid Detergent
261 Fibre), which contains mainly cellulose and lignin; and ADL (Acid Detergent Lignin),
262 corresponding to the lignin. Measurement uncertainties were 10% for NDF and ADF and
263 15% for ADL. Cellulose and hemicellulose were thus calculated by the subtractions ADF-
264 ADL and NDF-ADF, respectively.

265 The following two tests were carried out in triplicate in the laboratory. To determine the
266 proportion of water-soluble components, around 1 g of dried material (m_i , kg) and 100 mL of
267 distilled water were introduced into a flask and boiled for 1 h in a heating system with return
268 flow. The mixture was then separated by filtration on a sintered-glass filter. The flask and the
269 filter containing the sample were dried at 105°C and weighed to obtain the mass of
270 aggregates after boiling (m_f , kg) by deducting the tare weights t_1 (flask) and t_2 (filter). The
271 water-soluble content (WS) was determined according to equation 6:

$$WS (\%) = \frac{m_i - m_f}{m_i} \times 100 \quad (6)$$


272 To determine the mineral matter content, around 1 g of dried material (m_i) was heated at
273 550°C for 7 h in a crucible of tare weight t . After cooling in a desiccator, the ash was weighed
274 in the crucible (m_f). Mineral matter content (MM) was calculated with equation 7:

$$MM (\%) = \frac{m_f - t}{m_i} \times 100 \quad (7)$$

275
276 The coefficients of variation were between 10 and 18% and between 2 and 8% for extractive
277 and ash contents respectively.
278

279 2.5. Sorption-desorption isotherms

280 The sorption-desorption property is necessary to model the buffering effect of a material and
281 has great influence on its resistance to the proliferation of micro-organisms [34]. The
282 sorption-desorption isotherms of the 3 plant aggregates were evaluated by the Dynamic
283 Vapour Sorption (DVS) method. Temperature and relative humidity were regulated by the
284 device (Surface Measurement Systems, London, UK). The uncertainties of the device are \pm
285 0.01 mg for the microbalance, \pm 0.2°C for the PT100 thermometer and \pm 0.5% for the dew
286 point sensor. The specimen, suspended by a micro-balance, was weighed every 60 seconds.
287 Two specimens of each plant aggregate were tested and were assumed to be representative
288 of these very hygroscopic materials [45-47]. The mass of the samples tested was very low,
289 between 13 and 65 mg, due to the volume available in the sample holder. The samples were
290 composed of 10 to 20 plant particles. However, Bui et al. [47] have shown that a sample of
291 20 mg of cut straw shows quite a good representativeness on DVS measurements. Before
292 testing, the specimen was dried for 2 h at 50°C (using dry N₂ gas) in the DVS device. The
293 test was carried out at 23°C, which is the temperature specified in the standard for the
294 saturated salt solution method, NF EN ISO 12571 [48]. Relative humidity was regulated in
295 successive stages from 0 to 95% by steps of 10%, except for the last stage, which was equal
296 to 5%. For each step, the specimen was considered to have reached moisture balance if
297 $dm/dt < 5 \cdot 10^{-5} \text{ \%} \cdot \text{min}^{-1}$ over a ten-minute period [49] or in a maximum time interval of 360
298 minutes (twice this time for the last three steps). Fig.4 shows an example of straw sorption-
299 desorption behaviour with this programme. It can be seen that, at high relative humidity, the
300 change of step was triggered by the time criterion, which resulted in a slight underestimation
301 of the moisture content for the last three steps.

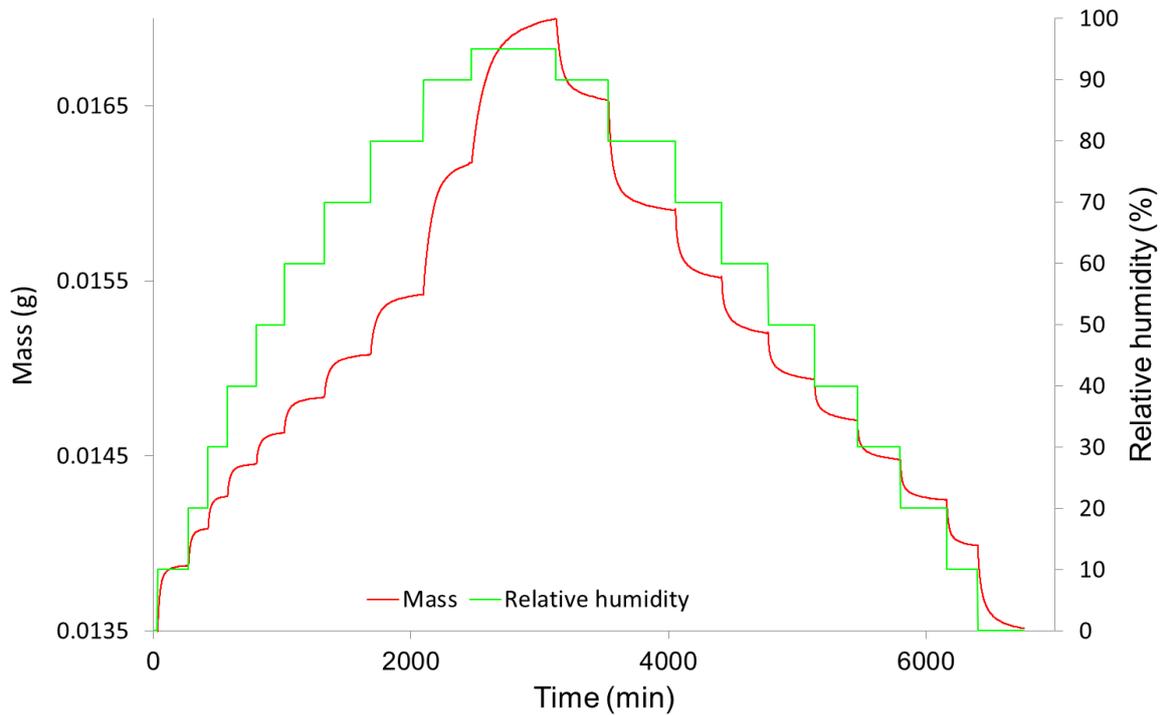

302


303 **Fig.4** Typical variation of mass and relative humidity for the DVS (here sorption-desorption of
 304 barley straw)

305 3. RESULTS AND DISCUSSION

306 3.1. Availability of by-products

307 Fig.5 represents the quantities of by-product produced (Bt) and available (Ba) for the 5
 308 families mentioned in the Material and Methods section. Production is greatest for the cereal
 309 straw family with 85 Mt/y, while the most available by-product is wood residue with 33 Mt/y.
 310 Nevertheless, the availability of cereal straw is 7 Mt/y.

311 The families of the three plant particles of the present study are framed in orange: barley
 312 straw, hemp shiv and corn cob, belonging respectively to cereal straws, industrial crops and
 313 agri-food industry by-products.

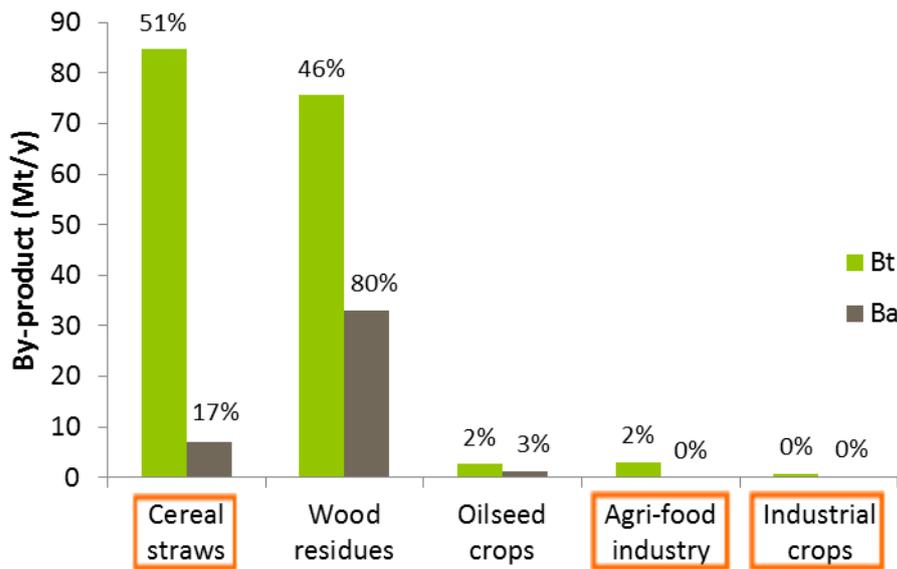

314




315 **Fig.5** Production and availability of different by-product families

316 The quantities of by-products produced are represented in Fig.6 for the 3 families
 317 (agricultural crops, agri-food industry and industrial crops). Production is presented rather
 318 than availability, because available resources are not reported by France Agrimer [18] or
 319 others for the agri-food industry and industrial by-products. The majority of agri-food industry
 320 by-products are used for animal fodder.

321 Cereal straw and stalks and oleaginous crops are included in agricultural crops. Barley straw
 322 makes up the second highest quantity produced in this category and the third most available
 323 crop by-product, with 4.3 Mt/y, after soft wheat straw and maize stalk. Much more cereal
 324 straw is produced than oleaginous straw (rape, sunflower and soya).

325 Corn cob is a by-product of the agri-food industry. It is included in corn by-product, along with
 326 leaf and damaged grain. The quantity of corn by-product produced is around 0.24 Mt/y,
 327 which makes it the fourth category produced in this family.

328 Hemp is the second most-produced industrial crop by-product after flax, with around 17
 329 thousand tons. This value is much lower than those of the other plant aggregates selected,
 330 but it is a plant by-product that has already been the subject of a number of studies for
 331 building materials. France is the biggest European hemp producer [27], and some
 332 professional rules exist [50]. This has led to the development of construction or rehabilitation
 333 of buildings with hemp concrete in the past 10 years.

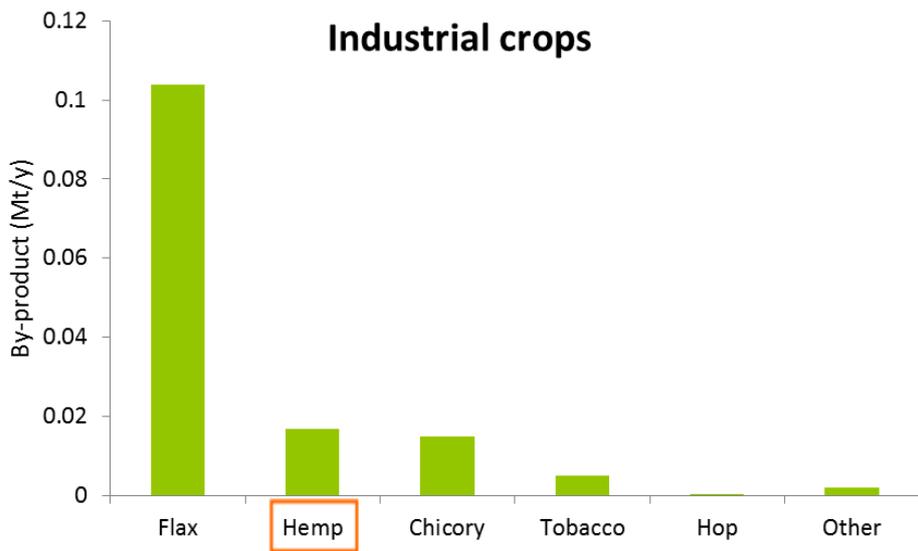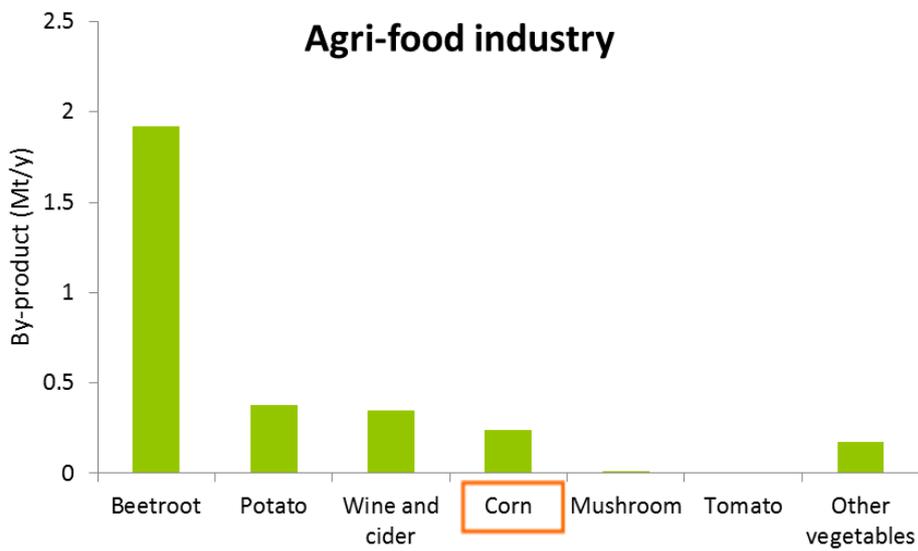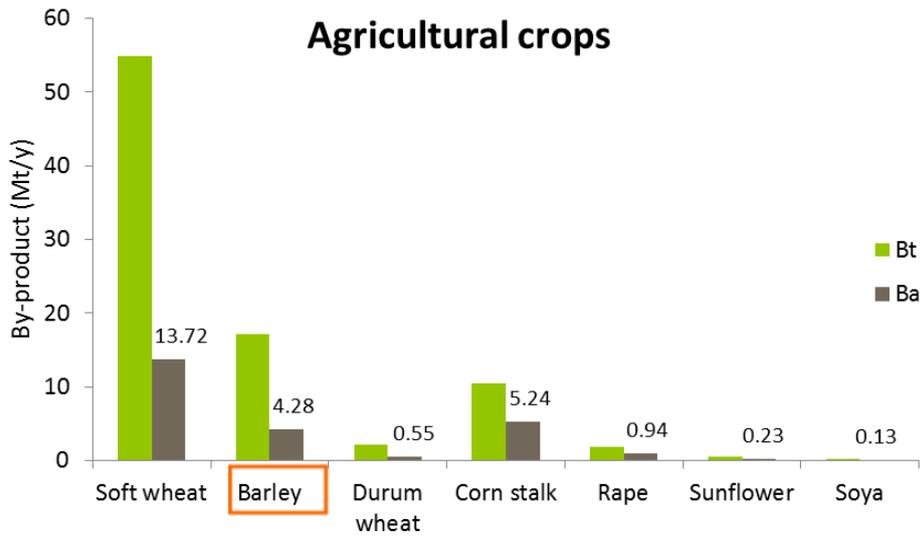

334 **Fig.6** Quantities of by-products from agricultural crops, agri-food industry and industrial crops

335 In France, various types of by-products are available, in different proportions. Cereal straws
336 are the greatest resource available. It is thus interesting to study barley straw in order to
337 develop new bio-composites promoting this kind of resource. Maize and hemp do not provide
338 the greatest quantities of by-products of their respective families. However, they both have
339 huge potential: maize is the cereal most produced in the world [36] and France is the biggest
340 hemp producer in Europe [27]. Forthcoming studies should focus on bioresources with
341 widespread availability, such as wood residues, which represent 80% of the by-products
342 available; flax, which yields around five times as much by-product as hemp; or beetroot
343 residue, which constitutes the largest by-product by weight from agro-industry.


344

345 3.2. Physical properties

346 3.2.1. Microscopic description

347 The morphology and porous structure of the plant particles are illustrated by the SEM images
348 of Fig.7.

349

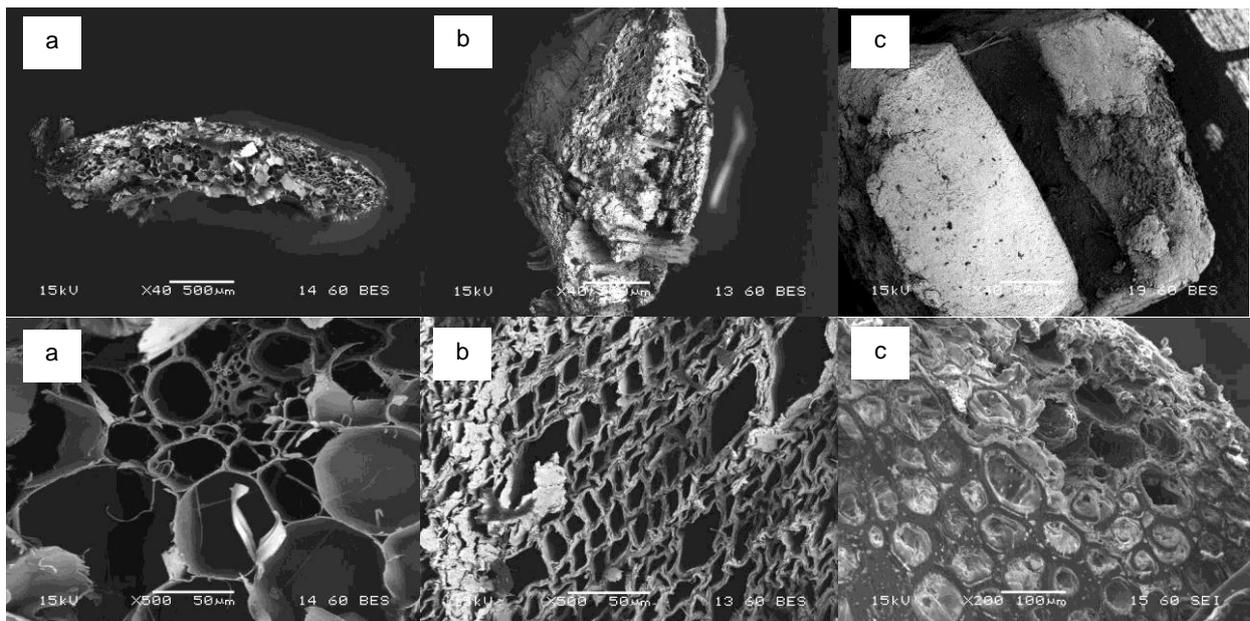

350 **Fig.7** SEM images of: (a) straw, (b) hemp shiv and (c) corn cob at low (first line) and high
351 (second line) magnification factors

352

353 These SEM images clearly show a tubular microstructure for the three materials. However,
354 some differences can be observed. The pores of the straw, from 2 to 100 µm, are multi-scale
355 and the cell walls are very thin (maximum thickness of 2 µm). Hemp shiv pores range from 5
356 to 40 µm and the particles present regular cell walls 4 µm thick on average. Concerning corn
357 cob, the diameter of the pores is between 20 and 80 µm with a thick cell wall of up to 45 µm.
358 The fact that the parenchyma is thicker for corn cob than for hemp shiv or straw indicates a

359 lower macro-porosity and thus a higher density of the plant particle. According to Pinto et al.
 360 [51], this could lead to a strength capacity comparable to that of soft woods.

361

362 *3.2.2. Particle size analysis*

363 The particle size distribution of plant aggregates seems to have an influence on the
 364 mechanical performance of bio-based building materials. For example, Millogo et al. have
 365 shown that the compressive strength of an earth-based composite with short pieces of straw
 366 (3 cm) is higher than that of similar composite with longer pieces (6 cm) [4]. Conversely, in
 367 the case of hemp concrete, it has been shown that the coarser the hemp shiv is, the higher is
 368 the mechanical performance at 28 days [11], [52]. Danso et al. [53] have studied the effect of
 369 fibre aspect ratio on mechanical strength in an earth matrix. Compressive and tensile
 370 strengths improved for coconut, oil palm and bagasse fibres when the major axes increased.
 371 In this study, the morphological characteristics of straw, hemp shiv and corn cob were
 372 compared. Dust content, determined by sieving at 500 µm, was about 7.2%, 2.1% and 0.3%
 373 respectively for the straw, hemp shiv and corn cob. The grading curves are presented in
 374 Fig.8. Averages and standard deviations of the major and minor axes, EAD or aspect ratio
 375 were calculated from equations 8 and 9 [40] and are presented in Table 1.

$$E_{am}(x) = \frac{\sum A_i(x_i)}{\sum A_i} \quad (8)$$


$$Sd_{am}(x) = \sqrt{\frac{\sum A_i(x_i - E_{am}(x))^2}{\sum A_i}} \quad (9)$$

376 where $E_{am}(x)$ is the arithmetic mean of the dimension x (Major, Minor, EAD or AR), A_i is the
 377 projected area of each particle detected (mm^2), x_i is the dimension of each particle detected
 378 and $Sd_{am}(x)$ is the associated standard deviation.

Dimension	Barley straw	Hemp shiv	Corn cob
Major (mm)	7.6 ± 4.4	5.6 ± 2.6	3.6 ± 0.8
Minor (mm)	2.3 ± 1.5	2.0 ± 1.2	2.6 ± 0.4
EAD (mm)	4.0 ± 2.1	3.3 ± 1.6	3.1 ± 0.5
AR	4.1 ± 3.7	3.3 ± 2.0	1.4 ± 0.4

379 **Table 1.** Arithmetic means and dispersions of plant aggregate dimensions

380 The standard deviations associated with the mean dimensions of barley straw and hemp shiv
 381 are higher than for the corn cob. This is due to the marked heterogeneity of these particles,
 382 which are obtained by mechanical grinding without any specific calibration process. In
 383 contrast, the standard deviation associated with the mean values of the corn cob
 384 morphological parameters is quite low since this aggregate is made up of a single granular
 385 fraction obtained after an industrial process of calibration.

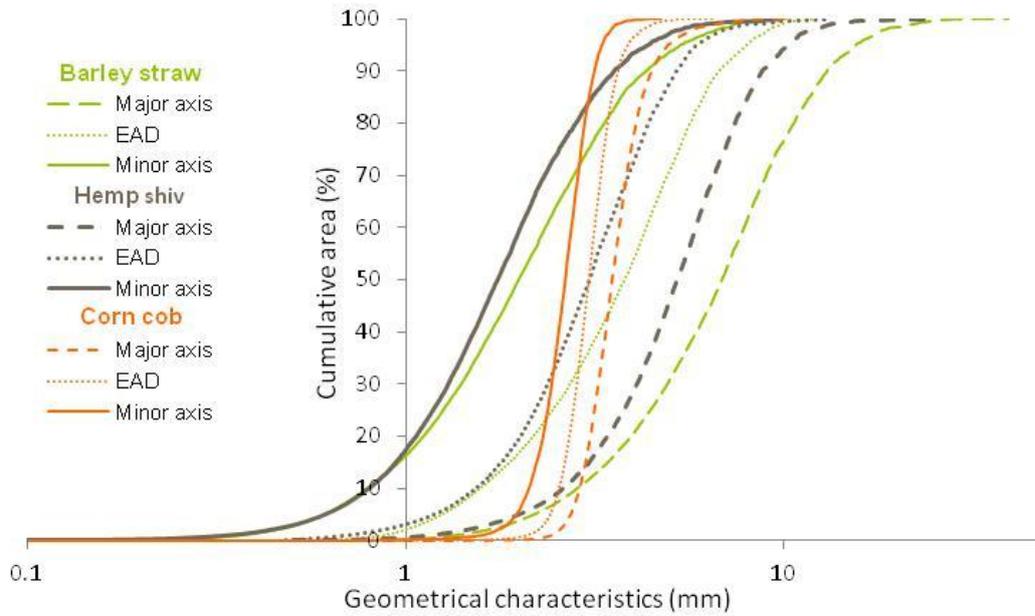


386

387 **Fig.8** Grading curves of the plant aggregates as a function of the cumulative area

388 It can be observed in Fig.8 that the corn cob spindle (between the major and minor axes) is
 389 the smallest and the steepest. This means that the major and minor axes are of similar
 390 length and the size of the particles is fairly regular. This result is understandable because
 391 corn cob is a calibrated material (by the Eurocob company). Grading curves are quite similar
 392 between straw and hemp shiv. The size of straw particles is just slightly larger than the size
 393 of hemp shiv particles.

394 Proportions of AR in cumulative area are represented in Fig.9.

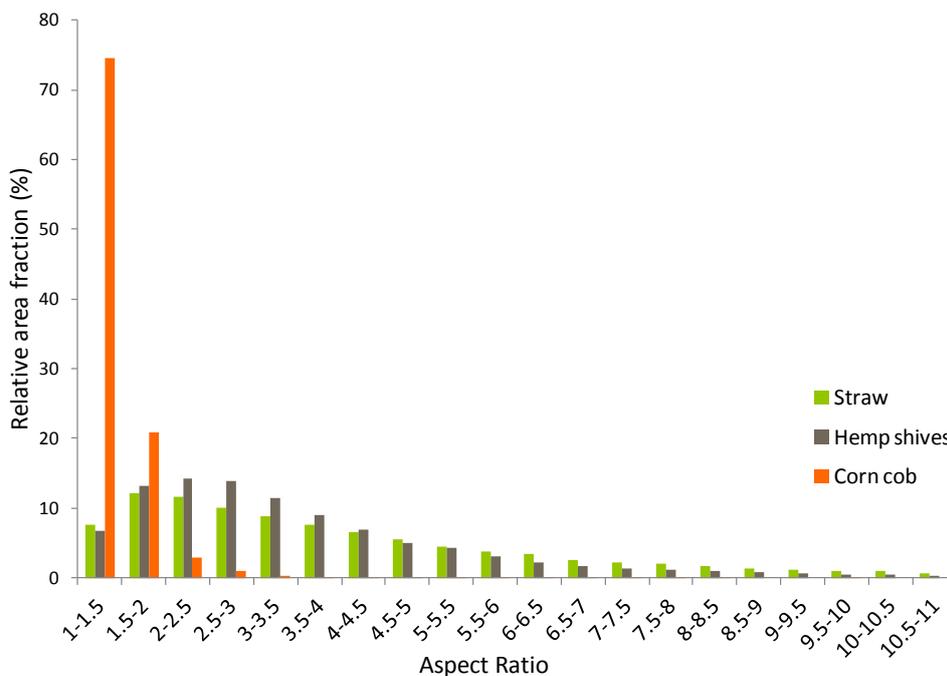


395

396 **Fig.9** Relative area distribution as a function of aspect ratio

397 It can be noted that the AR of corn cob is very close to 1, meaning that corn cob particles
 398 present a nearly circular cross section. Straw and hemp shiv are more elongated (especially
 399 straw) with more variation among particles.

400

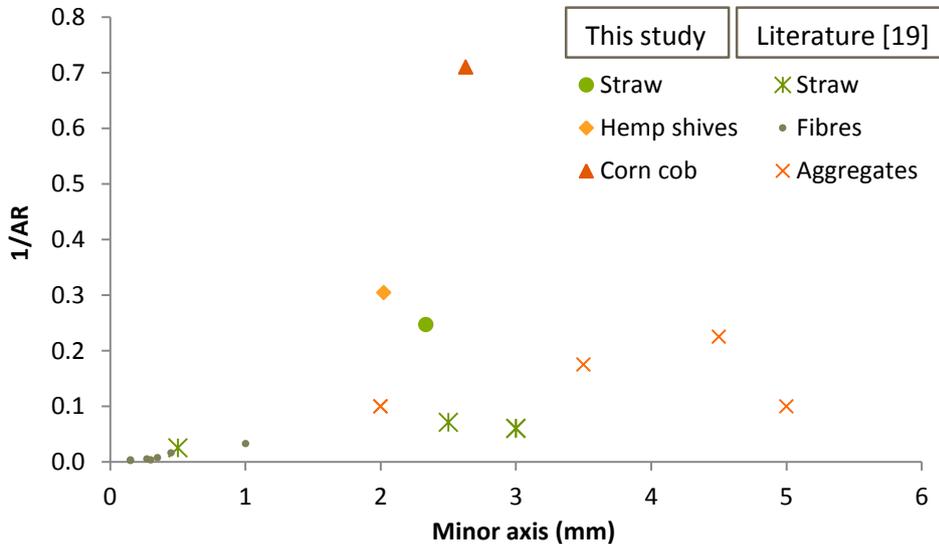

401

402 **Fig.10** Reciprocal of the aspect ratio as a function of average minor axis

403 In Fig.10, the reciprocal of the AR is represented as a function of the average minor axis, in
 404 order to be compared with some values found in the literature. The minor axis of this study
 405 was considered to be equivalent to the diameter of the literature. These values from the
 406 literature, quoted in a review by Laborel-Préneron et al. [19], were classified by type of
 407 particle: fibres, aggregates and straw. Their AR was lower than that of the aggregates
 408 studied here, although their minor axes were of the same order of magnitude as in the
 409 particles of this study. For the straw, this can be explained by the shortness of our particles
 410 even though the diameter was similar to those in the literature. Hemp shiv was more crushed
 411 and finer than in the literature and corn cob was almost spherical, which is not very common
 412 for plant aggregates.

413 Optimizing the particle size distribution could be an interesting lever to improve the
 414 compactness of the particle arrangement of bio-based building materials, as is common for
 415 basic concretes. The selection of specific particle fractions or the combination of particles
 416 with different morphologies could lead to an enhancement of their mechanical performances.

417

418 3.2.3. Bulk density and thermal conductivity

419 Using insulating materials in buildings is a way to save energy. Adding some vegetal
 420 particles into existing building materials such as earth or concrete is a means of reducing
 421 their density and thus improving their thermal insulation [6], [54]. Such particles can also be

422 applied in buildings as loose-fill insulation. Bulk density (Table 2) and thermal conductivity
 423 (Table 3) are presented together, because thermal conductivity is highly dependent on the
 424 density [19].

Plant aggregate	Barley straw	Hemp shiv	Corn cob
This study	57 ± 1	153 ± 2	497 ± 14
Literature	47 [55]	110.9 [9]	450 [58]
	116 [56]	148.3 [57]	495 [57]
		130 [29]	

425 **Table 2.** Bulk densities ($\text{kg}\cdot\text{m}^{-3}$) of the plant aggregates studied

426
 427 Table 2 presents the average bulk density of each plant aggregate with the standard
 428 deviation and some values from the literature. The values from this study are close to the
 429 values from literature, except for one value for barley straw. This difference may be due the
 430 length of the straw or the method used to measure it. Barley straw has the lowest bulk
 431 density, followed by hemp shiv and then corn cob, which has the highest. The coefficients of
 432 variation are 2.0, 1.6 and 2.8% respectively for straw, hemp shiv and corn cob. This value is
 433 lower than 5% which suggests good representativeness of the different samples.


Plant aggregate	Barley straw	Hemp shiv	Corn cob
This study	0.044 ± 0.001	0.051 ± 0.002	0.096 ± 0.001
Literature	0.035-0.054 [22]	0.058 [9]	0.099 [57]
		0.055 [28]	
		0.057 [42]	

435 **Table 3.** Thermal conductivity ($\text{W}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$) of the plant aggregates studied

436 Table 3 shows that the thermal conductivity values measured were similar to those found in
 437 the literature. The coefficients of variation are 1.4, 3.9 and 1.1% respectively for straw, hemp
 438 shiv and corn cob. This value is lower than 5% which suggests good representativeness of
 439 the different samples. Moreover, the water uptake during the test was lower than 0.2% for
 440 each specimen. The moisture content, influencing thermal conductivity, can thus be
 441 neglected.

442 Fig.11 compares the thermal conductivity of various plant aggregates from this study and the
 443 literature in function of their bulk densities. The relation plotted is linear: the lower the bulk
 444 density is, the lower is the thermal conductivity. Thermal conductivity depends mostly on the
 445 bulk density. However, there are small variations even within a given particle type. They can
 446 be explained by the difference in moisture content or in the testing method. The type of
 447 vegetal does not seem to influence the thermal conductivity significantly, but more results
 448 would be needed to confirm that hypothesis.

449 The barley straw and hemp shiv characterized in this study present bulk densities and
 450 thermal conductivities similar to those of loose-fill insulation materials such as cellulose
 451 wadding or glass fibre (quoted in Goodhew and Griffiths [59]). Maskell et al. [60]
 452 characterized other natural loose-fill insulation materials: wool, hemp fibre and wood fibre.
 453 Such lightweight aggregates could be used in great quantities in an earth matrix as was done
 454 by Labat et al. [5] with an earth clay material. The density was 241 kg.m^{-3} for a thermal
 455 conductivity of $0.071 \text{ W.m}^{-1}.\text{K}^{-1}$, much lower than for a traditional earth material, for which the
 456 corresponding values are between 1940 and 2007 kg.m^{-3} and 0.47 and $0.59 \text{ W.m}^{-1}.\text{K}^{-1}$ [49].
 457 As far as hemp concrete is concerned, it presents a thermal conductivity between 0.06 and
 458 $0.19 \text{ W.m}^{-1}.\text{K}^{-1}$ for a dry density between 200 and 840 kg.m^{-3} [29].
 459

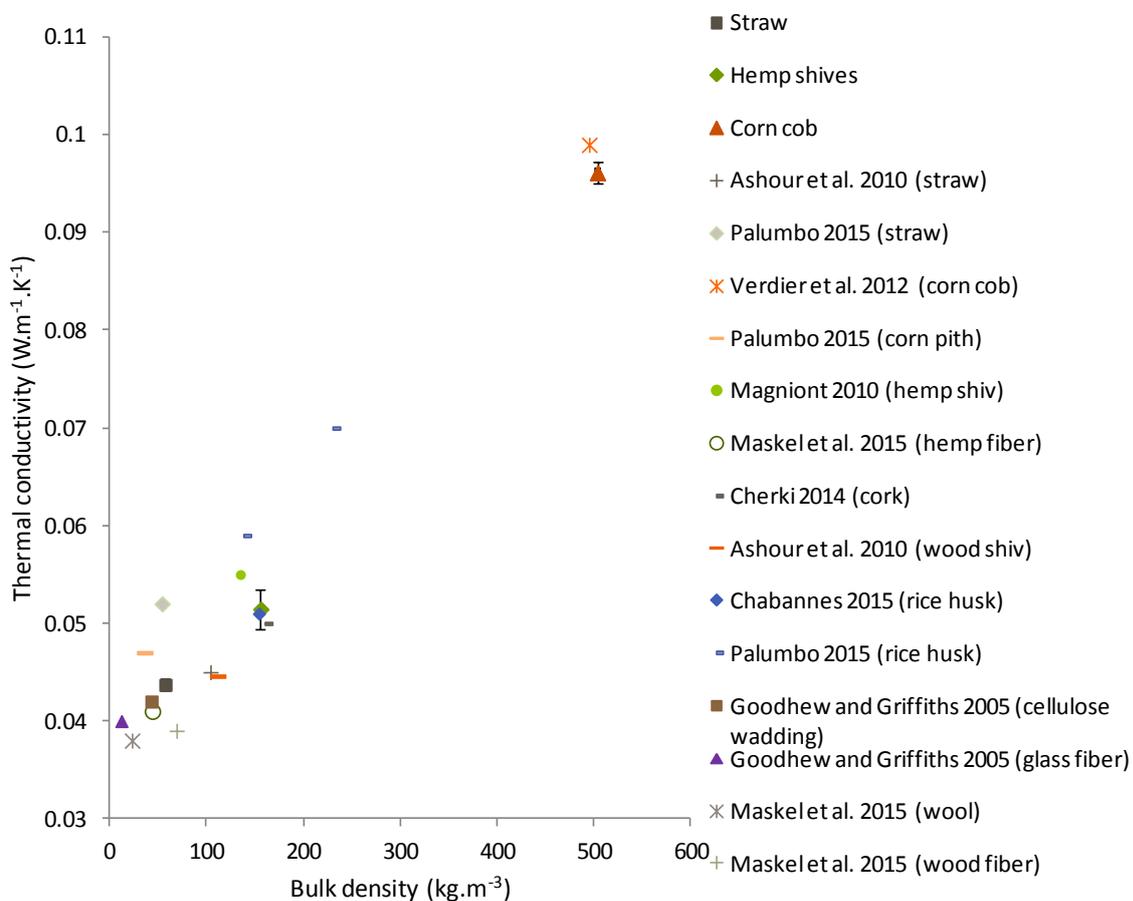

460
 461 **Fig.11** Comparison of thermal conductivity values measured experimentally for straw, hemp
 462 shiv and corn cob and values found in the literature
 463

464 These materials, especially barley straw and hemp shiv, could thus be used either as
 465 lightweight aggregates to improve the thermal insulation properties of an earth or mineral
 466 matrix, or as loose-fill insulation materials. A material is considered to be a thermal insulator
 467 when the thermal conductivity is lower than $0.065 \text{ W.m}^{-1}.\text{K}^{-1}$ [61]. However, the thermal
 468 conductivity found for these agro-resources was measured for particles in the dry state and it

469 is known that thermal conductivity increases with relative humidity [62]. The round robin tests
 470 of RILEM TC 236 BBM [35] revealed an increase of the thermal conductivity by 12.9%
 471 between the dry state and a relative humidity of 50%. If that increase is applied to the values
 472 measured for the dried plant aggregates, thermal conductivities become $0.049 \text{ W}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$ for
 473 straw, $0.058 \text{ W}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$ for hemp shiv and $0.109 \text{ W}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$ for corn cob. In the case of straw
 474 and hemp shiv, these estimated values are still lower than the value expected for an
 475 insulation material.

476

477 3.2.4. Water absorption


478 Within a hydraulic matrix, plant aggregate water absorption is an important formulation
 479 parameter as competition can occur between the particle absorption and the matrix hydration
 480 [9], leading to potential problems. Consequently, the amount of mixing water has to be
 481 largely overestimated. This implies a very long drying time, hardly compatible with the current
 482 rate of building. Water absorption was evaluated for up to 48 h for the three kinds of
 483 aggregates (Table 4).

484

Plant aggregate	Barley straw	Hemp shiv	Corn cob
This study	414 ± 4	380 ± 11	123 ± 2
Literature	500-600 [25] 400 [55]	280 [30] 301 [9] 406 [42]	90 [58] ~150 [57]

485 **Table 4.** Absorption capacity (%) after 48 h of immersion

486 Maximum absorption was 414% for straw followed by 380% for hemp shiv and 123% for corn
 487 cob in the present work. Calculating the coefficients of variation gave 1.1% for barley straw,
 488 2.8% for hemp shiv and 1.3% for corn cob. These values are lower than 5%, which indicates
 489 good representativeness. These retention capacities seemed to be consistent with the
 490 literature, which presents nevertheless a high range of water absorption. This high variability
 491 could be due to the diversity of the plant particle itself or to the test method used. Only the
 492 value from [9] was obtained with the same protocol. Absorbent paper was used in references
 493 [30], [57] and the method used was not specified in the other cases. The low water
 494 absorption of corn cob could be interesting because, according to Bouhicha et al. [25], a high
 495 retention capacity is not good for adhesion to a soil matrix. During the manufacturing
 496 process, the swelling of the particles engendered by water absorption in the first 24 hours
 497 pushes the soil away. Then, when the composite material dries, shrinkage creates voids
 498 around the particles at the interface with the soil [63].

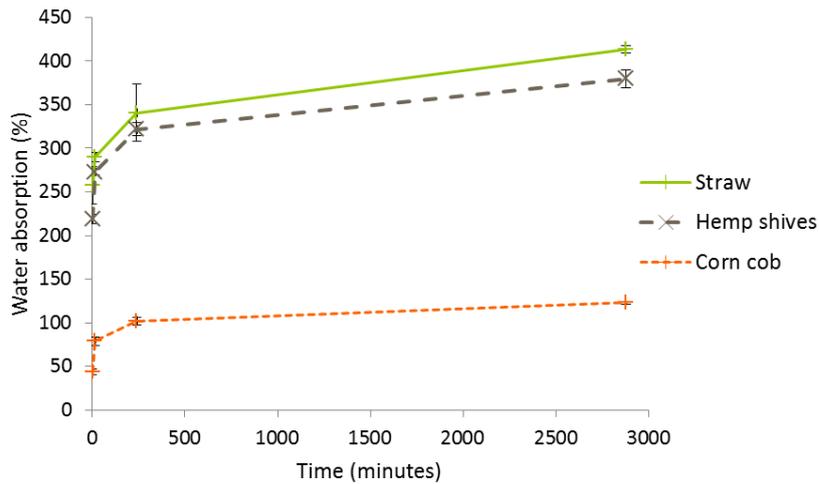


499

500 **Fig.12** Water absorption as a function of time

501 The kinetics of this absorption is presented in Fig.12. It is very fast for these plant
 502 aggregates: absorption by straw and hemp shiv at 1 minute is close to 60% of the final
 503 absorption (48 h) and 36% for corn cob. These curves can thus be considered in two parts:
 504 the first one, with fast kinetics, represents an absorption by capillarity forces in the pores
 505 filled by free water [12], [55]. The second one corresponds to a diffusion mechanism based
 506 on Fick's law in the micro-pores and water bonding through openings (20-40 nm) in the plant
 507 cell walls [64].

508 Water absorption occurs through the multi-scale porosity of the particles, especially for stems
 509 such as straw and hemp shiv, which transport the sap in the plant. This water content seems
 510 to be linked with the internal porosity of the material [41]. On the SEM pictures (Fig.7), high
 511 internal porosity can be seen for straw and hemp shiv. Corn cob is less porous and the water
 512 absorption is calculated from the particle mass, so the volume of water absorbed might not
 513 be very different from that found for straw and hemp shiv.

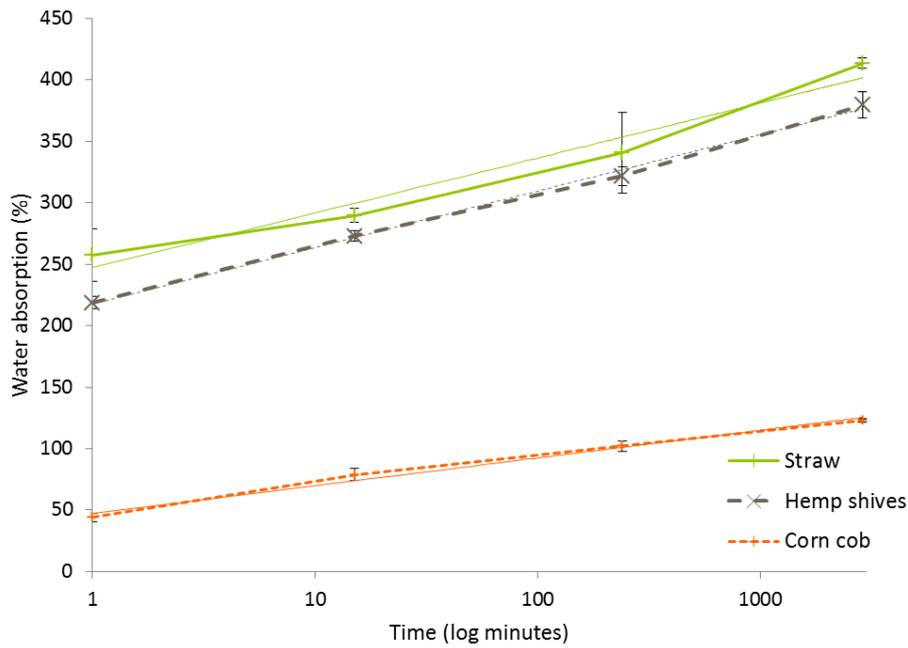

514
515 **Fig.13** Water absorption as a function of logarithm of time

516 This absorption can be represented as a function of logarithm of time (Fig.13), where the
517 curves of the equation:

$$W = IRA + K_1 \times \text{Log}(t) \quad (10)$$

518 proposed by Nozahic and Amziane [12], are linear. The Initial Rate of Absorption (IRA, %) is
519 the absorption relative to an immersion of 1 minute, representing the adsorption of external
520 water on the surface of the particles [65]. K_1 represents the diffusion rate in the cells (%.(log
521 min)⁻¹), the second part of the curve. Both values, IRA and K_1 , are recapitulated in Table 5,
522 with R^2 , the correlation coefficient between the experimental values and the straight line.

523

Plant aggregate	Barley straw	Hemp shiv	Corn cob
IRA ^a	247	218	48
K_1 ^b	19.4	19.9	9.8
R^2 ^c	0.9632	0.9972	0.9874

524 ^a IRA is the Initial Rate of Absorption; ^b K_1 represents the diffusion rate in the cells; ^c R^2
525 is the correlation coefficient

526 **Table 5.** Water absorption parameters

527 K_1 and IRA, to a lesser extent, of barley straw and hemp shiv are very close to each other.
528 However, the logarithmic representation of barley straw water absorption is less linear (R^2 of
529 0.96). The coefficient K_1 of corn cob is lower than the other two, meaning that the water
530 diffusion rate in the cells is quite low.

531 As previously commented, due to the high water absorption of barley straw and hemp shiv,
532 the amount of mixing water required should be increased if these particles are added to a
533 hydraulic binder [66]. This can lead to a problematic increase of the drying time after
534 demoulding [9]. However, different treatments could be applied to reduce the water
535 absorption and drying time. Some treatments can also increase the bonding between the
536 plant particles and the matrix. Nozahic and Amziane [12] studied three different treatments to
537 improve the adhesion of sunflower aggregates to a mineral matrix: pre-wetting by an alkaline
538 solution, a linseed oil coating, and a paraffin wax coating, which showed the best efficiency.
539 Other plant aggregate treatments were studied in the case of an earth matrix, such as
540 acetylation, rosin-alcohol coating or thermal immersion in boiling water, and are summarized
541 in Laborel-Préneron et al. [19].

542

543 3.3. Chemical characterization

544 The chemical characterization of plant aggregates is important in the case of bio-composites
545 with hydraulic binder as chemical composition can influence their properties or those of the
546 composites, such as setting time or hydration mechanisms.

547 Lignocellulosic raw materials are composed of three main components: cellulose,
548 hemicellulose and lignin. There are also other chemical species present such as pectin,
549 extractives and ash. Cellulose, a polymer containing various alcoholic hydroxyl groups, can
550 significantly affect the mechanical performance of the fibres [67]. Hemicellulose is a highly
551 hydrophilic component, easily hydrolysed by acids and soluble in dilute alkali solutions. This
552 could thus influence the water absorption of the plant particle and affect its durability in an
553 alkaline mineral matrix, such as cement or lime, and the bonding mechanisms at the
554 interface in these composite materials [68]. Lignin is a polymer able to protect the stem of the
555 plant from chemical or physical aggressions, notably from most microbial attacks. The nature
556 and the amount of lignin thus affect the durability and the biodegradability of the distinct
557 vegetal materials [67]. A variety of functions is attributed to pectins, including mechanical
558 properties, cell-cell adhesion, wall porosity and binding of ions [69]. An affinity between
559 pectin and cations exists and could affect the setting mechanisms of mineral binders
560 (Portland cement, lime, etc.) used in bioaggregate-based composites.

561

562 These interactions can take place at different times. At early age, they can disturb the setting
563 and hardening mechanisms of mineral binders. Hemp shiv [70], hemp fibres [71], wood
564 particles [72-75], cereal straw [76], [77] (cited in [78]), arhar stalks [79], sugar cane bagasse
565 [80] and coir particles [81], among others, have been shown to negatively impact the setting
566 and early hardening of cement paste. Wood particles can also be associated with a plaster
567 matrix (calcium sulfate hemihydrate). Boustingorry et al. [82] emphasized that poplar and

568 forest pine extracts clearly delayed the hydration of hemihydrate. Finally, the setting of a
 569 pozzolanic binder (mix of lime and metakaolin) has been shown to be affected by the
 570 presence of lavender stalks [13]. In the hardened state, they can modify the properties of the
 571 composite. Poor cohesion has been observed between plant aggregates and the mineral
 572 matrix, associated with a powdering of the binder [70]. In the long term, they can influence
 573 the durability of the material through mineralization of the plant aggregates by cement
 574 hydration products [83]. This engenders a loss of ductility of the fibres, which is a
 575 disadvantage for plant fibre reinforced concrete, which has to work in flexion. However, it
 576 might be an advantage for bioaggregate-based composites, leading to a continuous
 577 enhancement of compressive strength [84].

578

579 The chemical composition of the three plant aggregates is presented in Table 6 and
 580 compared with some other values from the literature. Values are expressed in percentage of
 581 dry mass of the plant material. The column “Extractives” refers to the water-soluble content
 582 (this study), the sum of pectin, wax, fat and protein, or the content obtained with Soxhlet
 583 extraction (literature).


584

Aggregate	Reference	Lignin (%)	Cellulose (%)	Hemicellulose (%)	Extractives (%)	Ash (%)
Barley straw	This study	5.5	37.7	26.7	14.4	12.3
	[85]	15.8	37.6	34.9	-	-
	[86]	15	46	23	-	-
Hemp shiv	This study	17.2	50.3	17.9	5.9	2.1
	[87]	18	52	9	-	2
	[88]	22.1	37.7	26.8	8.9	-
	[70]	21.8-23.3	45.6-49.2	17.8-21	5.1-6.2	2.6-3.7
	[89], [90]	28	48	12	10	2
	[91]	28	44	18	10	2
	[92]	23	44	25	4	1.2
Corn cob	This study	6.6	41.4	40.7	6.9	1.4
	[58]	6.8	47.1	37.3	-	1.2
	[93]	6.7-13.9	32.5-45.6	39.8	-	-
	[68]	14.7	48.1	37.2	7	-

585 **Table 6.** Chemical composition of the 3 plant aggregates

586 Among the three types of particles studied, barley straw showed the highest amount of
 587 extractives (14.4%) and ash (12.3%). The extractive contents of hemp shiv and corn cob
 588 were 5.2 and 6.9%, respectively. The ash content of these two aggregates was also lower, at
 589 2.1 and 1.4%. It is important to take the extractives content into account because it is the
 590 main cause of interactions with the hydraulic binder.

591 These chemical compositions are represented in a ternary diagram showing lignin, cellulose
 592 and hemicellulose (Fig.14).The values are normalized to 100%, as in [68]. The comparison of
 593 the composition of particles is facilitated by this presentation. The plant aggregates used in
 594 this study are circled in red.

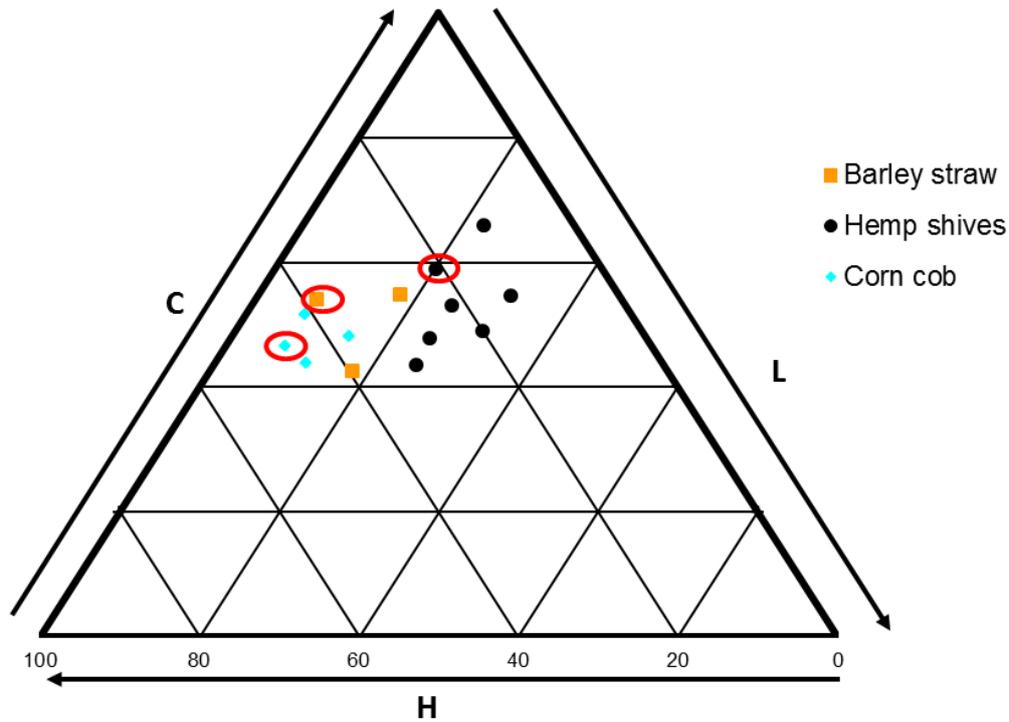


595
 596 **Fig.14** Chemical composition of the 3 plant aggregates

597 All the bioaggregates were rich in cellulose, which several authors link to the mechanical
 598 performance of the aggregate [67], [94], [95]. Corn cob was the aggregate presenting the
 599 highest hemicellulose content, a component easily dissolved by alkaline attack. It is thus the
 600 least usable in an alkaline mineral matrix. The lignin content was higher for hemp shiv. This
 601 aggregate could thus be the most durable of the three types.

602 Values for a type of aggregate are quite scattered. These variations may be due to the
 603 measurement method used but may also be connected with differences in the maturity of the
 604 stems, the season of harvest, the variety or, in the case of hemp, the retting process [96].

605
 606 3.4. Sorption-desorption isotherms (DVS)

607 Fig.15 presents the sorption-desorption isotherms of the 3 plant aggregates.

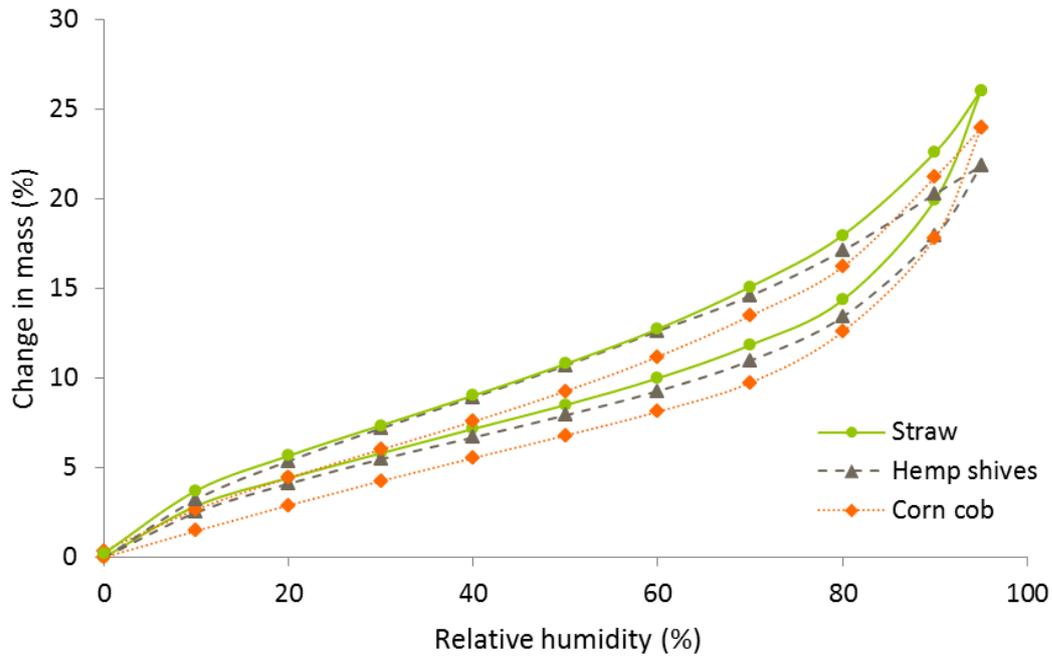


608

609 **Fig.15** DVS water vapour sorption isotherm of the 3 plant aggregates at 23°C

610 The shape of the sorption curves is similar for all the particles and corresponds to a
 611 sigmoidal isotherm, Type II according to the IUPAC (International Union of Pure and Applied
 612 Chemistry) classification. This result is very common for cellulosic and lignocellulosic
 613 materials [34]. Although the results are similar for the three aggregate types, straw has a
 614 slightly higher sorption value at high relative humidity (but below 90% of relative humidity),
 615 followed by hemp shiv and corn cob.

616

617 Hysteresis (Fig.16) represents the gap between the sorption and desorption isotherms
 618 (moisture content in desorption is higher than in sorption). This phenomenon is commonly
 619 explained by capillary condensation, the ink-bottle effect and the contact angle difference
 620 between adsorption and desorption [97], [98]. This phenomenon also seems to be influenced
 621 by the lignin content of the natural fibres [98]. The hysteresis values, ranging from 0.1 to
 622 3.8%, increase with relative humidity except for the last 1 or 2 steps. They are comparable
 623 for the three plant particles.

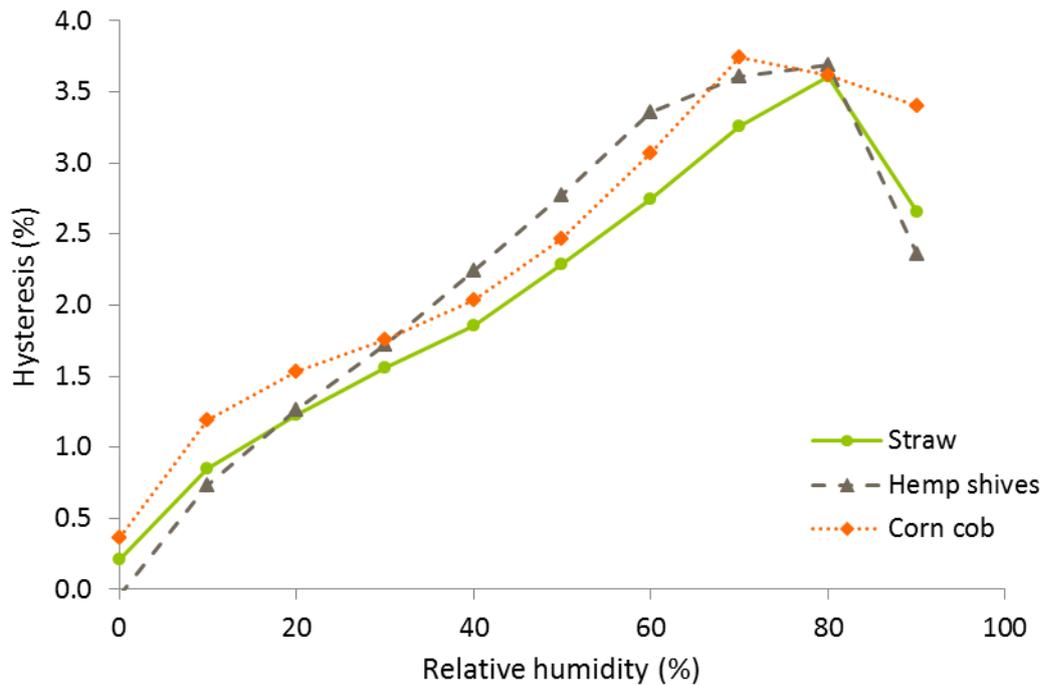

624

625 **Fig.16** Hysteresis calculated from the sorption and desorption isotherms of the 3 plant
 626 aggregates at 23°C

627 These plant aggregates, whose sorption values reach 20 to 26% at 95% of relative humidity,
 628 could be used as aggregates in a matrix to increase the sorption capacity of the material. A
 629 high sorption capacity could induce good moisture buffering if the kinetics of sorption-
 630 desorption proved to be fast. This would improve the balance of the indoor air humidity,
 631 making it more comfortable for the occupant [99]. Complementary tests to study the kinetics
 632 of the sorption and desorption of each materials would be necessary to conclude on the
 633 subject of moisture buffering. This improvement has already been studied by Ashour et al.
 634 [100] with straw added to an earth plaster. The sorption capacity improved from 1.7% for
 635 earth alone to 6.5% with the addition of 75% of straw by volume.

636 At 80% RH, the sorption capacity of a lime plaster studied by Černý et al. 2006 [101] was
 637 lower than 1% and those of pozzolanic lime plasters were up to 4%. The sorption capacity of
 638 the plant aggregates of this study was between 12 and 14%. Their addition to that kind of
 639 mineral matrix could increase the sorption capacity of the composite material.

640

641 4. CONCLUSION

642 In this paper, three potential resources for bio-based building materials were characterized:
 643 barley straw, hemp shiv and corn cob. Their availability in France, physical properties,
 644 chemical composition and hygric properties were investigated. This overall methodology is
 645 mostly adapted from the RILEM method for characterizing bio-based aggregates. Although
 646 the round robin test was performed for hemp shiv, it can be adapted to other plant particles:

647 the mass of the samples should be modified according to the bulk density of the particle type.
648 However, image analysis may be less useful in the case of spherical particles, such as corn
649 cob, which can be characterized by the faster sieving method, as is done for mineral
650 aggregate. The study of the availability of plants was deliberately restricted to France, as the
651 use of local resources allows the environmental impact to be limited. Nevertheless, this kind
652 of investigation should be carried out to evaluate the potential each time an agro-resource is
653 considered for the development of a new bio-based material.

654 The main results are summarized below:

- 655 • Barley straw is a resource having good availability, with more than 4 million tons available
656 each year. Corn cob and hemp shiv also present an interesting potential with 240000 and
657 17000 tons of by-products available each year.
- 658 • The microstructure of these three aggregates is composed of tubular pores, but with a
659 different cell wall thickness for each type.
- 660 • Bulk density, highly dependent on these microstructures, is around 60,150 and 500 kg.m⁻³
661 respectively for the straw, hemp shiv and corn cob.
- 662 • Thermal conductivity is, like bulk density, the lowest for straw, followed by hemp shiv and
663 then corn cob.
- 664 • The morphology of the particles is quite similar for straw and hemp shiv (the straw being
665 slightly more elongated) whereas corn cob aggregate is more spherical. That property
666 could lead to different qualities of adhesion in case of use in a matrix.
- 667 • Water absorption is very high for straw and hemp shiv (414% and 380% respectively
668 after 48h of immersion) but it is much lower for corn cob, with only 123% of water
669 absorption.
- 670 • The chemical composition of the bioaggregates is rich in cellulose. Corn cob is rich in
671 hemicellulose, hemp shiv has the highest lignin content (17%) and straw presents the
672 highest extractive and ash content (around 25%).
- 673 • Sorption-desorption isotherms are similar for the three types of particles.

674 Some conclusions can thus be drawn for each particle type. Barley straw is the most
675 available agro-resource of this study and the best thermal insulator thanks to its low bulk
676 density. A major drawback is its high water absorption which would be prejudicial in case of
677 introduction of this straw into a pozzolanic or hydraulic matrix. It would induce the need for a
678 surplus of water leading to a longer drying time. However, there are some possibilities for
679 treating the particles to reduce this absorption and avoid its negative effects on adhesion or
680 setting time. Straw also presents the highest aspect ratio, which seems to be a positive factor
681 in terms of mechanical strength in an earth matrix [53]. Hemp shiv appears to be the most
682 suitable plant aggregate for use within a hydraulic matrix thanks to its lowest hemicellulose

683 and extractive contents. The thermal conductivity of both straw and hemp shiv is compatible
684 with their use as loose-fill insulation. As far as corn cob is concerned, its use might be
685 interesting because of its low water absorption, which would avoid the earth to be expanded.
686 However, its high hemicellulose content, sensitive to alkaline attack, limits its use in a
687 pozzolanic or hydraulic matrix for example.

688 All three plant aggregates could be used in an earth matrix, where there is no risk of
689 interaction. The high vapour sorption capacity of these lignocellulosic materials could be
690 useful to improve the capacity of earth or mineral matrices to store moisture. Concerning
691 morphological parameters, it has been shown that mechanical strength is higher when
692 coarser particles are incorporated [52]. However, complementary studies will be necessary to
693 correlate morphological parameters or size distribution of the plant particles with the
694 performances of the composites. These bioaggregates show promise for the development of
695 bio-based building materials if they are used in an appropriate matrix. More research is
696 needed in order to study other parameters such as mechanical strength, fire resistance or
697 microbial growth resistance. Other available resources should also be investigated to
698 develop new building materials, with beetroot for instance.

699

700 ACKNOWLEDGEMENTS

701 The authors wish to thank the French National Research Agency - France (ANR) for funding
702 project BIOTERRA - ANR - 13 - VBDU - 0005 Villes et Bâtiments Durables.

703

704 REFERENCES

- 705 [1] European Commission, "Buildings." 2016.
- 706 [2] Ministère de l'Environnement, de l'Energie et de la Mer, "Bâtiments et villes durables -
707 Déchets du bâtiment." 2012.
- 708 [3] A. Shea, M. Lawrence, and P. Walker, "Hygrothermal performance of an experimental
709 hemp-lime building," *Constr. Build. Mater.*, vol. 36, pp. 270–275, Nov. 2012.
- 710 [4] Y. Millogo, J.-C. Morel, J.-E. Aubert, and K. Ghavami, "Experimental analysis of
711 Pressed Adobe Blocks reinforced with Hibiscus cannabinus fibers," *Constr. Build.
712 Mater.*, vol. 52, pp. 71–78, 2014.
- 713 [5] M. Labat, C. Magniont, N. Oudhof, and J.-E. Aubert, "From the experimental
714 characterization of the hygrothermal properties of straw-clay mixtures to the numerical
715 assessment of their buffering potential," *Build. Environ.*, vol. 97, pp. 69–81, 2016.
- 716 [6] K. Al Rim, A. Ledhem, O. Douzane, R. M. Dheilly, and M. Queneudec, "Influence of the
717 proportion of wood on the thermal and mechanical performances of clay-cement-wood
718 composites," *Cem. Concr. Compos.*, vol. 21, no. 4, pp. 269–276, 1999.

- 719 [7] F. Aymerich, L. Fenu, and P. Meloni, "Effect of reinforcing wool fibres on fracture and
720 energy absorption properties of an earthen material," *Constr. Build. Mater.*, vol. 27, no.
721 1, pp. 66–72, Feb. 2012.
- 722 [8] P. Tronet, T. Lecompte, V. Picandet, and C. Baley, "Study of lime hemp composite
723 precasting by compaction of fresh mix — An instrumented die to measure friction and
724 stress state," *Powder Technol.*, vol. 258, pp. 285–296, May 2014.
- 725 [9] T. M. Dinh, "Contribution to the development of precast hempcrete using innovative
726 pozzolanic binder," PhD dissertation in Civil Engineering, Université Toulouse III - Paul
727 Sabatier, Toulouse, 2014.
- 728 [10] C. Niyigena *et al.*, "Variability of the mechanical properties of hemp concrete," *Mater.*
729 *Today Commun.*, vol. 7, pp. 122-133, 2016.
- 730 [11] L. Arnaud and E. Gourlay, "Experimental study of parameters influencing mechanical
731 properties of hemp concretes," *Constr. Build. Mater.*, vol. 28, no. 1, pp. 50–56, Mar.
732 2012.
- 733 [12] V. Nozahic and S. Amziane, "Influence of sunflower aggregates surface treatments on
734 physical properties and adhesion with a mineral binder," *Compos. Part Appl. Sci.*
735 *Manuf.*, vol. 43, no. 11, pp. 1837–1849, Nov. 2012.
- 736 [13] V. Ratiarisoa, C. Magniont, S. Ginestet, C. Oms, and G. Escadeillas, "Assessment of
737 distilled lavender stalks as bioaggregate for building materials: Hygrothermal properties,
738 mechanical performance and chemical interactions with mineral pozzolanic binder"
739 *Constr. Build. Mater.*, vol. 124, pp. 801–815, Oct. 2016.
- 740 [14] M. de Wit and A. Faaij, "European biomass resource potential and costs," *Biomass*
741 *Bioenergy*, vol. 34, no. 2, pp. 188–202, Feb. 2010.
- 742 [15] G. Fischer, S. Prieler, H. van Velthuizen, S. M. Lensink, M. Londo, and M. de Wit,
743 "Biofuel production potentials in Europe: Sustainable use of cultivated land and
744 pastures. Part I: Land productivity potentials," *Biomass Bioenergy*, vol. 34, no. 2, pp.
745 159–172, Feb. 2010.
- 746 [16] K. Ericsson and L. J. Nilsson, "Assessment of the potential biomass supply in Europe
747 using a resource-focused approach," *Biomass Bioenergy*, vol. 30, no. 1, pp. 1–15, Jan.
748 2006.
- 749 [17] M. Palumbo, J. Avellaneda, and A. M. Lacasta, "Availability of crop by-products in
750 Spain: New raw materials for natural thermal insulation," *Resour. Conserv. Recycl.*, vol.
751 99, pp. 1–6, 2015.
- 752 [18] France Agrimer, "L'observatoire national des ressources en biomasse - Evaluation des
753 ressources disponibles en France." France Agrimer, 2015.

- 754 [19] A. Laborel-Préneron, J. E. Aubert, C. Magniont, C. Tribout, and A. Bertron, "Plant
755 aggregates and fibers in earth construction materials: A review," *Constr. Build. Mater.*,
756 vol. 111, pp. 719–734, 2016.
- 757 [20] J.-E. Aubert, A. Marcom, P. Oliva, and P. Segui, "Chequered earth construction in
758 south-western France," *J. Cult. Herit.*, vol. 16, no. 3, pp. 293–298.
- 759 [21] E. Quagliarini and S. Lenci, "The influence of natural stabilizers and natural fibres on
760 the mechanical properties of ancient Roman adobe bricks," *J. Cult. Herit.*, vol. 11, no. 3,
761 pp. 309–314, Jul. 2010.
- 762 [22] T. Ashour, H. Wieland, H. Georg, F.-J. Bockisch, and W. Wu, "The influence of natural
763 reinforcement fibres on insulation values of earth plaster for straw bale buildings,"
764 *Mater. Des.*, vol. 31, no. 10, pp. 4676–4685, Dec. 2010.
- 765 [23] L. Turanli and A. Saritas, "Strengthening the structural behavior of adobe walls through
766 the use of plaster reinforcement mesh," *Constr. Build. Mater.*, vol. 25, no. 4, pp. 1747–
767 1752, Apr. 2011.
- 768 [24] Ş. Yetgin, Ö. Çavdar, and A. Çavdar, "The effects of the fiber contents on the mechanic
769 properties of the adobes," *Constr. Build. Mater.*, vol. 22, no. 3, pp. 222–227, Mar. 2008.
- 770 [25] M. Bouhicha, F. Aouissi, and S. Kenai, "Performance of composite soil reinforced with
771 barley straw," *Cem. Concr. Compos.*, vol. 27, no. 5, pp. 617–621, May 2005.
- 772 [26] P. Faria, T. Santos, and J.-E. Aubert, "Experimental characterization of an earth eco-
773 efficient plastering mortar," *J. Mater. Civ. Eng.*, vol. 28, no. 1, 2016.
- 774 [27] Nomadéis, "Etude sur le secteur et les filières de production des matériaux et produits
775 bio-sourcés utilisés dans la construction (à l'exception du bois)." 2012.
- 776 [28] C. Magniont, "Contribution à la formulation et à la caractérisation d'un écomatériau de
777 construction à base d'agroressources," PhD dissertation in Civil Engineering,
778 Université Toulouse III - Paul Sabatier, Toulouse, 2010.
- 779 [29] V. Cerezo, "Propriétés mécaniques, thermiques et acoustiques d'un matériau à base de
780 particules végétales: approche expérimentale et modélisation théorique," PhD
781 dissertation in Civil Engineering, Institut National des Sciences Appliquées, Lyon, 2005.
- 782 [30] C. Flament, "Valorisation de fines de lavage de granulats : application à la construction
783 en terre crue," PhD dissertation in Civil Engineering, Université d'Artois, Béthune, 2013.
- 784 [31] E. Hamard, J.-C. Morel, F. Salgado, A. Marcom, and N. Meunier, "A procedure to
785 assess the suitability of plaster to protect vernacular earthen architecture," *J. Cult.*
786 *Herit.*, vol. 14, no. 2, pp. 109–115, Mar. 2013.
- 787 [32] J. Pinto *et al.*, "Corn's cob as a potential ecological thermal insulation material," *Energy*
788 *Build.*, vol. 43, no. 8, pp. 1985–1990, Aug. 2011.

- 789 [33] T. Verdier, C. Magniont, and G. Escadeillas, "Etude comparative de 3 types de
790 particules végétales en vue de leur incorporation comme granulats légers dans une
791 matrice minérale," presented at the NoMaD, Toulouse, France, 2012.
- 792 [34] M. Palumbo, "Contribution to the development of new bio-based thermal insulation
793 materials made from vegetal pith and natural binders," PhD Thesis, Universitat
794 Politècnica de Catalunya, Barcelona, 2015.
- 795 [35] S. Amziane, F. Collet, M. Lawrence, C. Magniont, and V. Picandet, "Round robin test for
796 hemp shiv characterisation," in *Bio-aggregates based building materials - State-of-the-
797 Art Report of the RILEM Technical Committee 236-BBM*, Springer., vol. 23, Sofiane
798 Amziane, Florence Collet, 2017.
- 799 [36] FAOSTAT, "Statistical pocketbook - World food and agriculture." 2015.
- 800 [37] Agreste, "Statistique agricole annuelle." 2014.
- 801 [38] D. Jölli and S. Giljum, "Unused biomass extraction in agriculture, forestry and fishery."
802 Sustainable Europe Research Institute (SERI), 2005.
- 803 [39] FCBA, "Mémento 2015." 2015.
- 804 [40] V. Picandet, "Characterization of Plant-Based Aggregates," in *Bio-aggregate-based
805 Building Materials*, S. Amziane, L. Arnaud, and N. Challamel, Eds. Hoboken, NJ 07030
806 USA: John Wiley & Sons, Inc., 2013, pp. 27–74.
- 807 [41] M. Chabannes, V. Nozahic, and S. Amziane, "Design and multi-physical properties of a
808 new insulating concrete using sunflower stem aggregates and eco-friendly binders,"
809 *Mater. Struct.*, vol. 48, no. 6, pp. 1815–1829, Jun. 2015.
- 810 [42] V. Nozahic, S. Amziane, G. Torrent, K. Saïdi, and H. De Baynast, "Design of green
811 concrete made of plant-derived aggregates and a pumice–lime binder," *Cem. Concr.
812 Compos.*, vol. 34, no. 2, pp. 231–241, Feb. 2012.
- 813 [43] M. Chabannes, J.-C. Bénézet, L. Clerc, and E. Garcia-Diaz, "Use of raw rice husk as
814 natural aggregate in a lightweight insulating concrete: An innovative application,"
815 *Constr. Build. Mater.*, vol. 70, pp. 428–438, 2014.
- 816 [44] AFNOR, "NF V18-122 - Aliments des animaux - Détermination séquentielle des
817 constituants pariétaux - Méthode par traitement aux détergents neutre et acide et à
818 l'acide sulfurique." 2013.
- 819 [45] F. McGregor, A. Heath, E. Fodde, and A. Shea, "Conditions affecting the moisture
820 buffering measurement performed on compressed earth blocks," *Build. Environ.*, vol.
821 75, pp. 11–18, May 2014.
- 822 [46] C. Feng, H. Janssen, Y. Feng, and Q. Meng, "Hygric properties of porous building
823 materials: Analysis of measurement repeatability and reproducibility," *Build. Environ.*,
824 vol. 85, pp. 160–172, Feb. 2015.

- 825 [47] R. Bui, M. Labat, and J.-E. Aubert, "Comparison of the Saturated Salt Solution and the
826 Dynamic Vapor Sorption techniques based on the measured sorption isotherm of
827 barley straw," *Accepted in Constr. Build. Mater.*, 2017.
- 828 [48] AFNOR, "Performance hygrothermique des matériaux et produits pour le bâtiment -
829 Détermination des propriétés de sorption hygroscopique." NF EN ISO 12571, 2013.
- 830 [49] H. Cagnon, J. E. Aubert, M. Coutand, and C. Magniont, "Hygrothermal properties of
831 earth bricks," *Energy Build.*, vol. 80, pp. 208–217, Sep. 2014.
- 832 [50] Association Construire en Chanvre, "Exécution d'ouvrages en bétons de chanvre : mur
833 en béton de chanvre, isolation de sol en béton de chanvre, isolation de toiture en béton
834 de chanvre, enduits en mortier de chanvre (Règles professionnelles)." Société d'édition
835 du bâtiment et des travaux publics, 2012.
- 836 [51] J. Pinto *et al.*, "Characterization of corn cob as a possible raw building material," *Constr.*
837 *Build. Mater.*, vol. 34, pp. 28–33, Sep. 2012.
- 838 [52] T. T. Nguyen, "Contribution à l'étude de la formulation et du procédé de fabrication
839 d'éléments de construction en béton de chanvre," PhD dissertation in Civil Engineering,
840 Université de Bretagne-SUD, 2010.
- 841 [53] H. Danso, D. B. Martinson, M. Ali, and J. Williams, "Effect of fibre aspect ratio on
842 mechanical properties of soil building blocks," *Constr. Build. Mater.*, vol. 83, pp. 314–
843 319, May 2015.
- 844 [54] H. Binici, O. Aksogan, M. N. Bodur, E. Akca, and S. Kapur, "Thermal isolation and
845 mechanical properties of fibre reinforced mud bricks as wall materials," *Constr. Build.*
846 *Mater.*, vol. 21, no. 4, pp. 901–906, 2007.
- 847 [55] M. Bouasker, N. Belayachi, D. Hoxha, and M. Al-Mukhtar, "Physical characterization of
848 natural straw fibers as aggregates for construction materials applications," *Materials*,
849 vol. 7, no. 4, pp. 3034–3048, Apr. 2014.
- 850 [56] B. Belhadj, M. Bederina, Z. Makhloufi, A. Goullieux, and M. Quéneudec, "Study of the
851 thermal performances of an exterior wall of barley straw sand concrete in an arid
852 environment," *Energy Build.*, vol. 87, pp. 166–175, Jan. 2015.
- 853 [57] T. Verdier, C. Magniont, and G. Escadeillas, "Valorisation de granulats végétaux dans
854 un matériau de construction à matrice minérale," presented at the Colloque
855 International Francophone NoMaD, Toulouse, France, 2012.
- 856 [58] Eurocob, Corn cob products, "Product specifications, EU-GRITS 8/10." 2003.
- 857 [59] S. Goodhew and R. Griffiths, "Sustainable earth walls to meet the building regulations,"
858 *Energy Build.*, vol. 37, no. 5, pp. 451–459, May 2005.
- 859 [60] D. Maskell *et al.*, "Properties of bio-based insulation materials and their potential impact
860 on indoor air quality," presented at the First International Conference on Bio-based
861 Building Materials, Clermont-Ferrand, France, 2015.

- 862 [61] D. Molle and P.-M. Patry, *RT 2012 et RT Existant: réglementation thermique et*
863 *efficacité énergétique*. Editions Eyrolles, 2011.
- 864 [62] H. Bal, Y. Jannot, N. Quenette, A. Chenu, and S. Gaye, "Water content dependence of
865 the porosity, density and thermal capacity of laterite based bricks with millet waste
866 additive," *Constr. Build. Mater.*, vol. 31, pp. 144–150, 2012.
- 867 [63] M. Segetin, K. Jayaraman, and X. Xu, "Harakeke reinforcement of soil–cement building
868 materials: Manufacturability and properties," *Build. Environ.*, vol. 42, no. 8, pp. 3066–
869 3079, Aug. 2007.
- 870 [64] W. . Banks, "Water uptake by scots pine sapwood, and its restriction by the use of water
871 repellents," *Wood Sci. Technol.*, vol. 7, pp. 271–284, 1973.
- 872 [65] C. Groot and J. Larbi, "The influence of water flow (reversal) on bond strength
873 development in young masonry," *Heron*, vol. 44, no. 2, 1999.
- 874 [66] H. M. Algin and P. Turgut, "Cotton and limestone powder wastes as brick material,"
875 *Constr. Build. Mater.*, vol. 22, no. 6, pp. 1074–1080, Jun. 2008.
- 876 [67] A. Mohanty, M. Misra, and L. Drzal, *Natural Fibers, Biopolymers, and Biocomposites*,
877 CRC Press. 2005.
- 878 [68] S. V. Vassilev, D. Baxter, L. K. Andersen, C. G. Vassileva, and T. J. Morgan, "An
879 overview of the organic and inorganic phase composition of biomass," *Fuel*, vol. 94, pp.
880 1–33, Apr. 2012.
- 881 [69] D. Mohnen, "Pectin structure and biosynthesis," *Curr. Opin. Plant Biol.*, vol. 11, no. 3,
882 pp. 266–277, Jun. 2008.
- 883 [70] Y. Diquélou, E. Gourlay, L. Arnaud, and B. Kurek, "Impact of hemp shiv on cement
884 setting and hardening: Influence of the extracted components from the aggregates and
885 study of the interfaces with the inorganic matrix," *Cem. Concr. Compos.*, vol. 55, pp.
886 112–121, Jan. 2015.
- 887 [71] D. Sedan, C. Pagnoux, A. Smith, and T. Chotard, "Mechanical properties of hemp fibre
888 reinforced cement: Influence of the fibre/matrix interaction," *J. Eur. Ceram. Soc.*, vol. 28,
889 no. 1, pp. 183–192, 2008.
- 890 [72] F. Jorge, C. Pereira, and J. Ferrera, "Wood-cement composites: a review," *Holz Roh*
891 *Werkst*, no. 62, pp. 370–377, 2008.
- 892 [73] B. Na, Z. Wang, H. Wang, and X. Lu, "Wood-cement compatibility review," *Wood Res.*,
893 vol. 5, no. 59, pp. 813–826, 2014.
- 894 [74] A. Govin, A. Peschard, and R. Guyonnet, "Modification of cement hydration at early
895 ages by natural and heated wood," *Cem. Concr. Compos.*, vol. 28, no. 1, pp. 12–20,
896 Jan. 2006.

- 897 [75] G. Vaickelionis and R. Vaickelioniene, "Cement hydration in the presence of wood
898 extractives and pozzolan mineral additives," *Ceram. - Silik.*, vol. 2, no. 50, pp. 115–122,
899 2006.
- 900 [76] M. Irle and H. Simpson, "Agricultural residues for cement-bonded composites,"
901 presented at the Moslemi A (ed) Inorganic-Bonded Wood and Fiber Composite Material
902 Conference Proceedings, 1996, vol. 5, pp. 54–58.
- 903 [77] E. Eusebio and M. Suzuki, "Production and properties of plant materials cement bonded
904 composites," *Bull. Exp. For. Lab. Tokyo Univ. Agric. Technol.*, p. 27, 1990.
- 905 [78] P. Soroushian, F. Aouadi, H. Chowdhury, A. Nossoni, and G. Sarwar, "Cement-bonded
906 straw board subjected to accelerated processing," *Cem. Concr. Compos.*, vol. 26, no. 7,
907 pp. 797–802, Oct. 2004.
- 908 [79] L. K. Aggarwal, S. P. Agrawal, P. C. Thapliyal, and S. R. Karade, "Cement-bonded
909 composite boards with arhar stalks," *Cem. Concr. Compos.*, vol. 30, no. 1, pp. 44–51,
910 Jan. 2008.
- 911 [80] K. Bilba, M.-A. Arsene, and A. Ouensanga, "Sugar cane bagasse fibre reinforced
912 cement composites. Part I. Influence of the botanical components of bagasse on the
913 setting of bagasse/cement composite," *Cem. Concr. Compos.*, vol. 25, no. 1, pp. 91–96,
914 Jan. 2003.
- 915 [81] G. A. M. Brasileiro, J. A. R. Vieira, and L. S. Barreto, "Use of coir pith particles in
916 composites with Portland cement," *J. Environ. Manage.*, vol. 131, pp. 228–238, Dec.
917 2013.
- 918 [82] P. Boustingorry, P. Grosseau, R. Guyonnet, and B. Guilhot, "The influence of wood
919 aqueous extractives on the hydration kinetics of plaster," *Cem. Concr. Res.*, vol. 35, no.
920 11, pp. 2081–2086, Nov. 2005.
- 921 [83] M. Ardanuy, J. Claramunt, and R. D. Toledo Filho, "Cellulosic fiber reinforced cement-
922 based composites: A review of recent research," *Constr. Build. Mater.*, vol. 79, pp. 115–
923 128, Mar. 2015.
- 924 [84] G. Balčiūnas, S. Vėjelis, S. Vaitkus, and A. Kairytė, "Modern building materials,
925 structures and techniques physical properties and structure of composite made by using
926 hemp hurds and different binding materials," *Procedia Eng.*, vol. 57, pp. 159–166, 2013.
- 927 [85] J. X. Sun, F. Xu, X. F. Sun, B. Xiao, and R. C. Sun, "Physico-chemical and thermal
928 characterization of cellulose from barley straw," *Polym. Degrad. Stab.*, vol. 88, no. 3, pp.
929 521–531, Jun. 2005.
- 930 [86] Z. Zhu, S. S. Toor, L. Rosendahl, D. Yu, and G. Chen, "Influence of alkali catalyst on
931 product yield and properties via hydrothermal liquefaction of barley straw," *Energy*, vol.
932 80, pp. 284–292, Feb. 2015.
- 933 [87] La chanvrière de l'Aube, "Kanabat, technical document." .

- 934 [88] B. De Groot, "Alkaline hemp woody core pulping - impregnation characteristics, kinetic
935 modelling and papermaking qualities," 1994.
- 936 [89] Y. Hustache and L. Arnaud, "Synthèse des connaissances sur les bétons et mortiers de
937 chanvre." *Fibres Recherche Développement*, Lhoist, Construire en Chanvre, 2008.
- 938 [90] C. Garcia-Jaldon and D. Dupeyre, "Fibres from semi-retted hemp bundles by steam
939 explosion treatment," *Biomass Bioenergy*, vol. 14, no. 3, pp. 251–260, Mar. 1998.
- 940 [91] M. R. Vignon, D. Dupeyre, and C. Garcia-Jaldon, "IEA Network-Biotechnology for the
941 conversion of lignocellulosics morphological characterization of steam-exploded hemp
942 fibers and their utilization in polypropylene-based composites," *Bioresour. Technol.*, vol.
943 58, no. 2, pp. 203–215, Nov. 1996.
- 944 [92] S. Gandolfi, G. Ottolina, S. Riva, G. P. Fantoni, and I. Patel, "Complete chemical
945 analysis of carmagnola hemp hurds and structural features of its components,"
946 *BioResources*, vol. 8, no. 2, pp. 2641–2656, Apr. 2013.
- 947 [93] P. Velmurugan *et al.*, "Monascus pigment production by solid-state fermentation with
948 corn cob substrate," *J. Biosci. Bioeng.*, vol. 112, no. 6, pp. 590–594, Dec. 2011.
- 949 [94] Y. Millogo, J.-E. Aubert, E. Hamard, and J.-C. Morel, "How properties of kenaf fibers
950 from Burkina Faso contribute to the reinforcement of earth blocks," *Materials*, vol. 8, no.
951 5, pp. 2332–2345, 2015.
- 952 [95] V. A. Alvarez and A. Vázquez, "Influence of fiber chemical modification procedure on
953 the mechanical properties and water absorption of MaterBi-Y/sisal fiber composites,"
954 *Compos. Part Appl. Sci. Manuf.*, vol. 37, no. 10, pp. 1672–1680, Oct. 2006.
- 955 [96] H.-R. Kymäläinen and A.-M. Sjöberg, "Flax and hemp fibres as raw materials for
956 thermal insulations," *Build. Environ.*, vol. 43, no. 7, pp. 1261–1269, Jul. 2008.
- 957 [97] F. Collet, M. Bart, L. Serres, and J. Miriel, "Porous structure and water vapour sorption
958 of hemp-based materials," *Constr. Build. Mater.*, vol. 22, no. 6, pp. 1271–1280, Jun.
959 2008.
- 960 [98] C. A. S. Hill, A. Norton, and G. Newman, "The water vapor sorption behavior of natural
961 fibers," *J. Appl. Polym. Sci.*, vol. 112, no. 3, pp. 1524–1537, 2009.
- 962 [99] M. Maddison, T. Mairing, K. Kirsimäe, and Ü. Mander, "The humidity buffer capacity of
963 clay–sand plaster filled with phytomass from treatment wetlands," *Build. Environ.*, vol.
964 44, no. 9, pp. 1864–1868, Sep. 2009.
- 965 [100] T. Ashour, H. Georg, and W. Wu, "An experimental investigation on equilibrium
966 moisture content of earth plaster with natural reinforcement fibres for straw bale
967 buildings," *Appl. Therm. Eng.*, vol. 31, no. 2–3, pp. 293–303, Feb. 2011.
- 968 [101] R. Černý, A. Kunca, V. Tydlitát, J. Drchalová, and P. Rovnaníková, "Effect of pozzolanic
969 admixtures on mechanical, thermal and hygric properties of lime plasters," *Constr.*
970 *Build. Mater.*, vol. 20, no. 10, pp. 849–857, Dec. 2006.

