



# Evidence of strong carrier localization below 100 K in a GaInNAs/GaAs single quantum well

L. Grenouillet, C. Bru-Chevallier, G. Guillot, P. Gilet, P. Duvaut, C. Vannuffel, A. Million, A. Chenevas-Paule

## ► To cite this version:

L. Grenouillet, C. Bru-Chevallier, G. Guillot, P. Gilet, P. Duvaut, et al.. Evidence of strong carrier localization below 100 K in a GaInNAs/GaAs single quantum well. Applied Physics Letters, 2000, 76 (16), pp.2241 - 2243. 10.1063/1.126308 . hal-01928830

**HAL Id: hal-01928830**

**<https://hal.science/hal-01928830>**

Submitted on 30 Nov 2018

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

## Evidence of strong carrier localization below 100 K in a GaInNAs/GaAs single quantum well

L. Grenouillet, C. Bru-Chevallier, G. Guillot, P. Gilet, P. Duvaut, C. Vannuffel, A. Million, and A. Chenevas-Paule

Citation: *Appl. Phys. Lett.* **76**, 2241 (2000); doi: 10.1063/1.126308

View online: <https://doi.org/10.1063/1.126308>

View Table of Contents: <http://aip.scitation.org/toc/apl/76/16>

Published by the American Institute of Physics

---

### Articles you may be interested in

“S-shaped” temperature-dependent emission shift and carrier dynamics in InGaN/GaN multiple quantum wells  
*Applied Physics Letters* **73**, 1370 (1998); 10.1063/1.122164

On the origin of carrier localization in  $\text{Ga}_{1-x}\text{In}_x\text{N}_y\text{As}_{1-y}/\text{GaAs}$  quantum wells  
*Applied Physics Letters* **78**, 1562 (2001); 10.1063/1.1354153

An analysis of temperature dependent photoluminescence line shapes in InGaN  
*Applied Physics Letters* **73**, 1697 (1998); 10.1063/1.122249

“Blue” temperature-induced shift and band-tail emission in InGaN-based light sources  
*Applied Physics Letters* **71**, 569 (1997); 10.1063/1.119797

Temperature quenching of photoluminescence intensities in undoped and doped GaN  
*Journal of Applied Physics* **86**, 3721 (1999); 10.1063/1.371242

Effect of temperature on the optical properties of (InGa)(AsN)/GaAs single quantum wells  
*Applied Physics Letters* **77**, 2870 (2000); 10.1063/1.1320849

---



**MMR**  
TECHNOLOGIES

**THE WORLD'S RESOURCE FOR  
VARIABLE TEMPERATURE  
SOLID STATE CHARACTERIZATION**



[WWW.MMR-TECH.COM](http://WWW.MMR-TECH.COM)

OPTICAL STUDIES SYSTEMS    SEEBECK STUDIES SYSTEMS    MICROPROBE STATIONS    HALL EFFECT STUDY SYSTEMS AND MAGNETS

# Evidence of strong carrier localization below 100 K in a GaInNAs/GaAs single quantum well

L. Grenouillet,<sup>a)</sup> C. Bru-Chevallier, and G. Guillot

*Laboratoire de Physique de la Matière, Institut National des Sciences Appliquées (UMR-CNRS-5511), Bât. 502, 20 Avenue A. Einstein, 69621 Villeurbanne Cedex, France*

P. Gilet, P. Duvaut, C. Vannuffel, A. Million, and A. Chenevas-Paule

*LETI/CEA-G-DOPT 17 Avenue des Martyrs, 38054 Grenoble Cedex 9, France*

(Received 20 October 1999; accepted for publication 24 February 2000)

We report an anomalous temperature dependence of the photoluminescence (PL) spectrum of a 7 nm  $\text{Ga}_{0.72}\text{In}_{0.28}\text{N}_{0.028}\text{As}_{0.972}/\text{GaAs}$  single quantum well. The PL peak energy exhibits an inverted S-shape dependence with temperature. Below 100 K, the PL integrated intensity shows a temperature dependence similar to that of amorphous semiconductors. The observed anomalous behavior is explained by a strong localization of carriers at low temperatures that could be induced by the presence of nitrogen. Thermal annealing does not significantly change the anomalous temperature dependence. © 2000 American Institute of Physics. [S0003-6951(00)04116-4]

The GaInNAs semiconductor alloy is being intensively studied for both its fundamental properties<sup>1,2</sup> and its potential for long wavelength optoelectronic device applications.<sup>3–5</sup> The incorporation of a low content of nitrogen in GaInAs reduces the band-gap energy significantly and allows emission wavelengths as long as 1.3  $\mu\text{m}$  to be reached.<sup>6</sup> The GaInNAs/GaAs material system is particularly promising for long wavelength vertical-cavity surface-emitting lasers on GaAs substrates. Such structures have already been reported.<sup>4,5</sup> However, the N incorporation generally induces degradation of the photoluminescence (PL) properties.<sup>6</sup> Therefore, the effect of nitrogen on the PL has to be well understood to be able to grow lasers with low threshold current densities. In this letter, we show that incorporation of a few percent of N in a GaInAs/GaAs single quantum well (SQW) changes the temperature dependence of the PL spectrum significantly. The observed anomalous behavior is explained by strong localization of carriers at low temperatures.

In this study, two samples were grown by gas source molecular beam epitaxy on semi-insulating 3 in. GaAs (100) substrates: a 7 nm  $\text{Ga}_{0.72}\text{In}_{0.28}\text{N}_{0.028}\text{As}_{0.972}/\text{GaAs}$  SQW structure and a 7 nm  $\text{Ga}_{0.72}\text{In}_{0.28}\text{As}/\text{GaAs}$  SQW structure as a reference sample. Both structures consist of a 350 nm thick GaAs buffer layer grown at 580 °C, the 7 nm SQW grown at 450 °C, and a 50 nm GaAs cap layer grown at 450 °C.<sup>7</sup> The surface morphologies of the structures are smooth and mirror like. The indium and nitrogen contents were estimated systematically by studying thick ternary alloys (GaInAs and GaAsN) in their strained states using high resolution x-ray rocking curve measurements. So the N percentage incorporated into GaInAs was assumed to be the same as that in the thick GaAsN layer. A 700 °C rapid thermal annealing for 10 min was carried out on the quaternary SQW under  $\text{N}_2$  flow. For PL measurements, the excitation was provided by the 514.5 nm line of an  $\text{Ar}^+$  laser focused on a 150  $\mu\text{m}$ -diam-spot with a power of 200 mW and chopped at a frequency of

17 Hz. The PL signal was detected through a HRS2 Jobin-Yvon monochromator by a liquid-nitrogen-cooled Ge photodiode associated with a standard lock-in technique. Photoreflectance (PR) spectroscopy is a modulation technique that enables the determination of intrinsic parameters in the band structure of semiconductors. A PR spectrum is the derivative of the absorption of the semiconductor. It exhibits first-derivative-like features at each direct transition in a SQW. The main optical transition in a SQW between the confined electron level and the confined hole level, called  $E_1H_1$ , can therefore be determined. PR measurements were recorded with conventional PR equipment.<sup>8</sup> For low temperature measurements, the samples were mounted in a variable temperature closed-cycle helium cryostat. Transmission electron microscopy (TEM) measurements were performed with an Akashi EM002B working at 200 kV.

PL and PR spectra of the as-grown GaInNAs/GaAs SQW are shown, respectively, in Figs. 1(a) and 1(b) at dif-

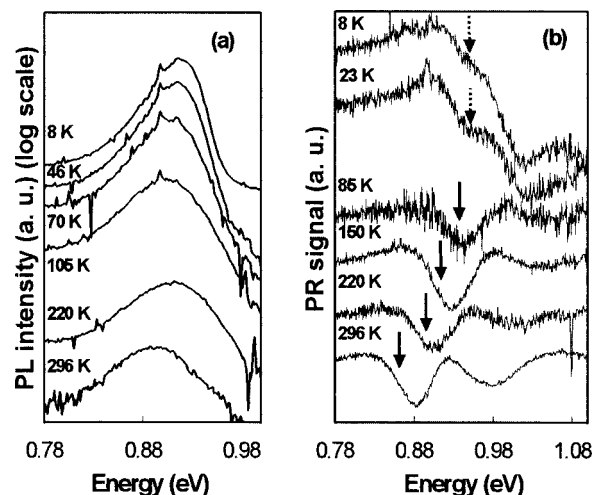


FIG. 1. PL (a) and PR (b) spectra of the as-grown GaInNAs/GaAs SQW recorded at various temperatures. The solid arrows in (b) indicate the  $E_1H_1$  energy fitted using the first-derivative form of the spectrum. The dashed arrows indicate the probable energy of the transition.

<sup>a)</sup>Electronic mail: lgrenouillet@cea.fr

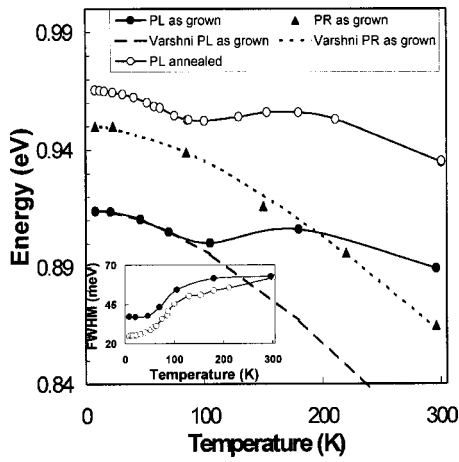


FIG. 2. PL temperature dependence of the emission peak of the GaInNAs/GaAs SQW, before (closed circles) and after (open circles) annealing. Solid lines are a guide to the eyes. Closed triangles represent the  $E_1H_1$  energy of the GaInNAs/GaAs SQW before annealing determined by PR measurements; the dotted line is a Varshni fit to these points. The dashed line is a Varshni fit to the closed circles in the 0–100 K region. The evolution of the FWHM of the PL peak with temperature, before (closed circles) and after (open circles) annealing is shown in the inset.

ferent temperatures. The emission peak energy increases only from 0.890 eV at 300 K to 0.914 eV at 8 K. The energy shift between 8 and 300 K is therefore very small: 25 meV. The PR spectrum exhibits first-derivative-like features above 85 K and  $E_1H_1$  is obtained through a nonlinear fit with a first-derivative functional form of the unperturbed dielectric function. Below that temperature, the spectrum has a step-like line shape as already observed in InAlAs alloys<sup>9</sup> and attribution of the  $E_1H_1$  energy is less accurate (taken in the middle of the step and indicated by dashed arrows).

Figure 2 shows the temperature dependence of the PL peak energy of the GaInNAs/GaAs SQW before and after annealing. It exhibits in both cases anomalous behavior, the so-called inverted S shape: from 8 to 100 K, the emission energy decreases, then increases from 100 to 175 K, and finally decreases again with temperature. This S-shape phenomenon has already been observed in alloys such as  $\text{Ga}_{0.5}\text{In}_{0.5}\text{P}$  (Ref. 10) and  $\text{Al}_{0.48}\text{In}_{0.52}\text{As}$  (Refs. 11–13) in InGaN/GaN multiple quantum wells<sup>14</sup> and in AlAs/GaAs disordered superlattices.<sup>15</sup> It was attributed to carrier localization. Also plotted in the inset of Fig. 2 is the evolution of the full width at half maximum (FWHM) of the PL peak with temperature, before and after annealing. Most of the increase in the FWHM takes place between 70 and 180 K, that is, in the inverted S-shape region. The annealing reduces the FWHM from 37 to 25 meV at 8 K. It also induces a 45–50 meV blueshift of the emission peak, described elsewhere.<sup>16</sup> Nevertheless, it does not significantly affect the inverted S-shape behavior and the FWHM dependence with temperature, indicating no major change in the PL processes.

The  $E_1H_1$  energy dependence with temperature measured by PR in the as-grown GaInNAs/GaAs SQW is also shown in Fig. 2. It does not exhibit S-shape behavior, but, rather, typical behavior that can be fitted by the empirical relation proposed by Varshni:<sup>17</sup>

$$E_g = E_0 - \alpha \times T^2 / (\beta + T), \quad (1)$$

with  $E_0 = 0.950$  eV,  $\alpha = 5.9 \times 10^{-4}$  eV/K, and  $\beta = 300$  K

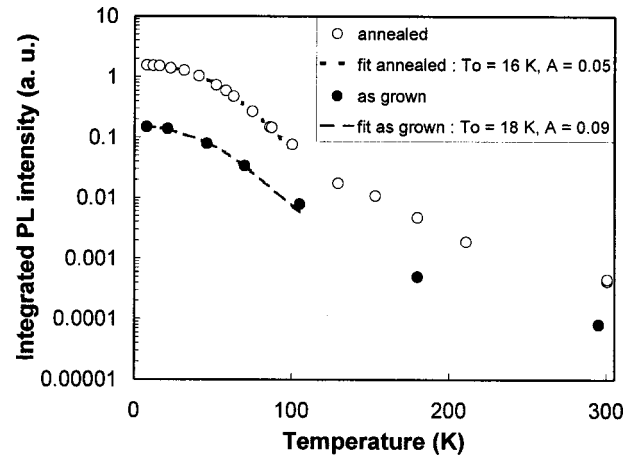


FIG. 3. Integrated PL intensity dependence with temperature of the GaInNAs/GaAs SQW emission peak before (closed circles) and after (open circles) annealing. Dashed and dotted lines are fits using the relation usually used for amorphous semiconductors.

(dotted line in Fig. 2). As the temperature decreases from 300 to 8 K, the energy shift between  $E_1H_1$  (closed triangles) and the emission peak (closed circles) therefore increases, showing that the PL emission at low temperatures arises from levels well below  $E_1H_1$ . At 300 K, the PR transition  $E_1H_1$  arises at an energy lower than the maximum of the PL peak. But this does not mean that the emission threshold lies higher than the absorption one, since the low-energy side of the PL spectrum remains below  $E_1H_1$ .

Since no inverted S-shape phenomenon was observed in the reference GaInAs/GaAs SQW, in which the temperature variation of the PL energy peak is described by Eq. (1) with  $E_0 = 1.234$  eV,  $\alpha = 5.5 \times 10^{-4}$  eV/K, and  $\beta = 300$  K, this suggests that the S-shape phenomenon is induced by the incorporation of nitrogen.

Figure 3 shows the temperature dependence of the GaInNAs/GaAs SQW integrated PL intensity, before and after annealing. Between 8 and 300 K, the integrated PL intensity drops by nearly four orders of magnitude. From 8 to 100 K, the quenching of the photoluminescence cannot be described by an Arrhenius plot, but, rather, by

$$I_{\text{PL}} = I_0 / [1 + A \times \exp(T/T_0)], \quad (2)$$

which is usually valid for amorphous semiconductors in which localization effects occur.<sup>18</sup>  $I_{\text{PL}}$  is the integrated PL intensity,  $T$  the measured temperature,  $T_0$  a characteristic temperature,  $A$  a tunneling factor, and  $I_0$  the integrated intensity at the low temperature limit.  $\text{Ga}_{0.5}\text{In}_{0.5}\text{P}$  (Ref. 10) and  $\text{Al}_{0.48}\text{In}_{0.52}\text{As}$  (Refs. 11 and 12) alloys exhibit the same dependence at low temperatures, as well as AlAs/GaAs disordered superlattices,<sup>15</sup> with  $T_0$  close to 18 and 16 K, the values derived from the as-grown and annealed GaInNAs/GaAs SQW, respectively. This shows further evidence of the localization of carriers in the GaInNAs/GaAs SQW at low temperatures. Above 100 K, the plot shows a discontinuity, indicating that the PL intensity versus temperature exhibits another dependence. Figure 3 also shows that annealing increases the PL intensity by one order of magnitude even though it does not change the integrated PL intensity dependence with temperature.

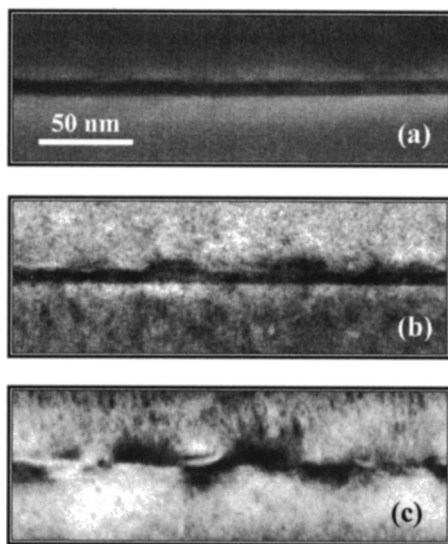


FIG. 4. Bright field cross-sectional TEM images of the as-grown GaInAs/GaAs (a) and GaInNAs/GaAs (b) SQWs. (c) (400) dark field image of the as-grown GaInNAs/GaAs SQW that reveals the strains.

The phenomena that induce the inverted S-shape behavior observed in the GaInNAs/GaAs SQW are now discussed. From 8 to 100 K, the quenching of the PL is typical of strong localization effects and the PL emission comes from energies below  $E_1H_1$ . Furthermore, in the 8–100 K range, the PL emission peak energy also has a temperature dependence that can be fitted well to Varshni dependence with  $E_0 = 0.914$  eV,  $\alpha = 7.0 \times 10^{-4}$  eV/K, and  $\beta = 300$  K, as shown in Fig. 2 (dashed line). Since coefficients  $\alpha$  and  $\beta$  are close to the ones we derived from the  $E_1H_1$  dependence with temperature, we therefore propose that, in this temperature region, the PL emission comes from localized states located a few tens of meV below  $E_1H_1$  and closely following the  $E_1H_1$  dependence with temperature. Around 100 K, some carriers have sufficient thermal energy to reach  $E_1H_1$ , so radiative recombinations come from both  $E_1H_1$  and the localized states. This is consistent with the increase in the FWHM of the broad peak in this region, which may be a sign of two different contributions to the PL peak. This also explains the increase in the PL emission peak energy as the temperature increases and the discontinuity in the plot of PL intensity versus temperature. As the temperature increases again, radiative recombination from  $E_1H_1$  become predominant: the decrease in the integrated PL intensity follows another regime and the PL energy peak decreases again with temperature, with a dependence that approaches the Varshni dependence followed by  $E_1H_1$ .

The physical origin of the localization effect is now investigated. Bright field cross-sectional TEM micrographs of the as-grown ternary and quaternary SQWs are shown in Figs. 4(a) and 4(b), respectively. Although the reference SQW shows flat interfaces and good homogeneity, it is observed from Fig. 4(b) that the incorporation of 2.8% nitrogen

induces well width fluctuations from 6 to 12 nm and local strain fluctuations as revealed by the dark field (400) image shown in Fig. 4(c). The origin of the localized states, from which originates the PL below 100 K, could be these well width and/or strain fluctuations, since carriers collected by the well preferentially locate in regions where the well width is maximum and/or the local strain minimum. It could also be composition fluctuations (In- and N-rich cluster regions) mentioned by Xin *et al.*<sup>19</sup> or even the existence of highly localized nitrogen-related deep levels in the band gap. However, in all cases nitrogen is most probably responsible for the localization of carriers, because localization effects are not observed in the nitrogen free reference sample.

In summary, both the energy and integrated intensity of the PL peak exhibit anomalous temperature behavior in a  $\text{Ga}_{0.72}\text{In}_{0.28}\text{N}_{0.028}\text{As}_{0.972}/\text{GaAs}$  SQW. This behavior, which is the consequence of nitrogen-induced localization effects, are not affected by annealing.

The authors thank G. Feuillet, H. Mariette, E. Molva, N. Pelekanos, and Le Si Dang for helpful discussions. This work was supported by a BRITE EuRam program, Contract No. BRPR-CT98-0721, Project No. BE97-4947.

- <sup>1</sup>W. Shan, W. Walukiewicz, J. W. Ager III, E. E. Haller, J. F. Geisz, D. J. Friedman, J. M. Olson, and S. R. Kurtz, *Phys. Rev. Lett.* **82**, 1221 (1999).
- <sup>2</sup>P. Perlin, S. G. Subramanya, D. E. Mars, J. Kruger, N. Shapiro, H. Siegle, and E. R. Weber, *Appl. Phys. Lett.* **73**, 3703 (1998).
- <sup>3</sup>M. Kondow, K. Uomi, A. Niwa, T. Kitatani, S. Watahiki, and Y. Yazawa, *Jpn. J. Appl. Phys., Part 1* **35**, 1273 (1996).
- <sup>4</sup>M. C. Larson, M. Kondow, T. Kitatani, K. Tamura, Y. Yazawa, and M. Okai, *IEEE Photonics Technol. Lett.* **9**, 1549 (1997).
- <sup>5</sup>C. Ellmers, F. Höhnsdorf, J. Koch, C. Agert, S. Leu, D. Karauskaj, M. Hofmann, W. Stolz, and W. W. Rühle, *Appl. Phys. Lett.* **74**, 2271 (1999).
- <sup>6</sup>H. P. Xin and C. W. Tu, *Appl. Phys. Lett.* **72**, 2442 (1998).
- <sup>7</sup>P. Gilet, A. Chenevas-Paule, P. Duvaut, L. Grenouillet, P. Holliger, A. Million, G. Rolland, and C. Vannuffel, *Phys. Status Solidi A* **176**, 279 (1999).
- <sup>8</sup>C. Bru, T. Benyattou, Y. Baltagi, S. Monéger, and G. Guillot, *J. Electrochem. Soc.* **93-27**, 214 (1993).
- <sup>9</sup>Y. Baltagi, E. Bearzi, C. Bru-Chevallier, T. Benyattou, G. Guillot, and J. C. Harmand, *Mater. Res. Soc. Symp. Proc.* **406**, 333 (1996).
- <sup>10</sup>F. A. J. M. Driessen, G. J. Bauhuis, S. M. Olsthoorn, and L. J. Giling, *Phys. Rev. B* **48**, 7889 (1993).
- <sup>11</sup>S. M. Olsthoorn, F. A. J. M. Driessen, A. P. A. M. Eijkelenboom, and L. J. Giling, *J. Appl. Phys.* **73**, 7798 (1993).
- <sup>12</sup>S. F. Yoon, Y. B. Miao, K. Radhakrishnan, and H. L. Duan, *J. Appl. Phys.* **78**, 1812 (1995).
- <sup>13</sup>I. T. Ferguson, T. S. Cheng, C. M. Sotomayor Torres, and R. Murray, *J. Vac. Sci. Technol. B* **12**, 1319 (1994).
- <sup>14</sup>Y.-H. Cho, G. H. Gainer, A. J. Fisher, J. J. Song, S. Keller, U. K. Mishra, and S. P. DenBaars, *Appl. Phys. Lett.* **73**, 1370 (1998).
- <sup>15</sup>T. Yamamoto, M. Kasu, S. Noda, and A. Sasaki, *J. Appl. Phys.* **68**, 5318 (1990).
- <sup>16</sup>R. Bhat, C. Caneau, L. Salamanca-Riba, W. Bi, and C. Tu, *J. Cryst. Growth* **195**, 427 (1998).
- <sup>17</sup>Y. P. Varshni, *Physica (Utrecht)* **34**, 149 (1967).
- <sup>18</sup>R. A. Street, T. M. Searle, and I. G. Augustin, in *Amorphous and Liquid Semiconductors*, edited by J. Stuke and W. Brenig (Taylor and Francis, London, 1974), p. 953.
- <sup>19</sup>H. P. Xin, K. L. Kavanagh, Z. Q. Zhu, and C. W. Tu, *Appl. Phys. Lett.* **74**, 2337 (1999).