



HAL
open science

Assessment of targeted non-intentionally added substances in cosmetics in contact with plastic packagings. Analytical and toxicological aspects

Pauline Murat, Pierre-Jacques Ferret, Sylvie Coslédan, Valérie Simon

► To cite this version:

Pauline Murat, Pierre-Jacques Ferret, Sylvie Coslédan, Valérie Simon. Assessment of targeted non-intentionally added substances in cosmetics in contact with plastic packagings. Analytical and toxicological aspects. *Food and Chemical Toxicology*, 2019, 128, pp.106-118. hal-02363272

HAL Id: hal-02363272

<https://hal.science/hal-02363272>

Submitted on 14 Nov 2019

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Open Archive Toulouse Archive Ouverte (OATAO)

OATAO is an open access repository that collects the work of Toulouse researchers and makes it freely available over the web where possible

This is an author's version published in: <http://oatao.univ-toulouse.fr/25059>

Official URL: <https://doi.org/10.1016/j.fct.2019.03.030>

To cite this version:

Murat, Pauline^{ORCID} and Ferret, Pierre-Jacques and Coslédan, Sylvie and Simon, Valérie^{ORCID} *Assessment of targeted non-intentionally added substances in cosmetics in contact with plastic packagings. Analytical and toxicological aspects.* (2019) *Food and Chemical Toxicology*, 128. 106-118. ISSN 0278-6915

Any correspondence concerning this service should be sent to the repository administrator: tech-oatao@listes-diff.inp-toulouse.fr

Assessment of targeted non-intentionally added substances in cosmetics in contact with plastic packagings. Analytical and toxicological aspects

Pauline Murat^{a,b}, Pierre-Jacques Ferret^c, Sylvie Coslédan^{a,*}, Valérie Simon^b

^aChimie Analytique et Compatibilité, Pierre Fabre Dermo-Cosmétique, 17 Allée Camille Soula, 31320, Vigoulez-Auzil, France

^bLaboratoire de Chimie Agro-Industrielle (LCA), Université de Toulouse, INRA, INPT, Toulouse, France

^cSécurité Produits et Cosmétovigilance, Pierre Fabre Dermo-Cosmétique, 3 Avenue Hubert Curien, 31035, Toulouse Cedex, France

ARTICLE INFO

Keywords:

Container-content interactions
Non-intentionally added substances
Gas chromatography-mass spectrometry
Packaging
Cosmetics
Safety assessment

ABSTRACT

Container-content interactions are common in the food and pharmaceutical industries. However, these studies are more complicated in the cosmetic industry, and it is necessary to ensure consumer safety. The objective of this work was to develop a strategy for the toxicological evaluation of leachables for cosmetic packagings. Eleven common plastic packagings were selected to evaluate interactions with 5 simulants (acidic, alkaline and neutral water, 30% and 96% ethanol) chosen to mimic cosmetics behavior. A GC-MS method was developed to screen for 12 non-intentionally added substances of particular concern: 10 phthalates, bisphenol A and distearyl thiodipropionate (European Pharmacopoeia plastic additive 17). Results were analyzed using a toxicological procedure established for this study. Some phthalates and bisphenol A were detected in several samples, but only one contaminant, diisobutyl phthalate (DiBP), was found to be above the set concentration threshold. Using toxicological data, this concentration was found to be safe for users. 96% ethanol appeared to be the strongest simulant in term of extraction, with a maximum concentration of 491 µg/L for DiBP in a 100% styrene-acrylonitrile copolymer packaging. In water simulants, less contaminants were extracted, with concentrations under 20 µg/L.

1. Introduction

Packaging in cosmetics plays an important role firstly for marketing purposes and secondly, and most importantly, for product protection against light or microbiological contamination. The complexity in developing a new packaging relies on the choice of the manufacturing material to have specific properties to achieve its desired functionality in the final type of container. Type of container also has an influence on the ease of use as well as on consumer safety through delivered dose (Gomez Berrada et al., 2017). A special consideration has to be taken with the different interactions that can exist between the content and packaging more commonly named as container content interactions (CCI). CCI studies are common in the food and pharmaceutical industries. They highlight the possible migration of molecules from the packaging to the product, which may impact the product quality, efficacy and consumer safety. European legislation has published regulations to define these studies: the European Pharmacopoeia (European Directorate for the Quality of Medicines & HealthCare (EDQM), 2013) for the pharmaceutical industry, regulation EC n°2017/745 for medical devices (European Parliament and Council of the European Union,

2017) and food regulations CE n°10/2011 (European Commission, 2011) and EC n°2018/213 (European Commission, 2018, p. 213) for the food and food contact packaging industries. The cosmetic industry is also concerned via cosmetic regulation EC n°1223/2009 (European Parliament and Council of the European Union, 2009). However, in contrast to the two other legislations, this document does not provide thresholds concerning authorized migration limits such as specific migration limits. The only information available for CCI studies are a list of prohibited substances and Article 17 stating that “the non intended presence of a small quantity of a prohibited substance, stemming from impurities of natural or synthetic ingredients, the manufacturing process, storage, migration from packaging, which is technically unavoidable in good manufacturing practice, shall be permitted provided that such presence is in conformity with Article 3”. Article 3 states that “a cosmetic product made available on the market shall be safe for human health [...]”. Certain substances are so prohibited when they are deliberately introduced but can be tolerated if they are proved to be non intentionally added and unavoidable. Annex 1 also attests that the cosmetic product safety report must contain information on impurities, traces and other pertinent facts concerning the packaging material

*Corresponding author.

E-mail address: sylvie.cosledan@pierre-fabre.com (S. Coslédan).

Abbreviations

| | | | |
|--------|---|--------|--|
| (r)PET | (recycled) PE terephthalate | IS | internal standard |
| ADD17 | Diethyl thiodipropionate (European Pharmacopoeia plastic additive n°17) | LLDPE | linear low density PE |
| BBP | benzylbutyl phthalate | LOD | limit of detection |
| BMD | benchmark dose | LOQ | limit of quantification |
| BPA | bisphenol A | MoS | margin of safety |
| CCI | container content interactions | MS | mass spectrometry |
| CMR | carcinogenic, mutagenic and reprotoxic (substances) | ND | not detected (below the LOD) |
| COEX | coextruded | NIAS | non intentionally added substances |
| DEHP | diethylhexyl phthalate | NOAEL | no observed adverse effect limit |
| DEP | diethyl phthalate | PE | polyethylene |
| DHP | dihexyl phthalate | PI | packaging item |
| DiBP | diisobutyl phthalate | PiPP | n pentyl isopentyl phthalate |
| DiPP | diisopentyl phthalate | PP | polypropylene |
| DMEP | bis(2 methoxyethyl) phthalate | REACH | Registration, Evaluation, Authorization and Restriction of Chemicals |
| DnBP | di n butyl phthalate | RfD | reference dose |
| DNEL | derived no effect level | SAN | styrene acrylonitrile copolymer |
| DnPP | di n pentyl phthalate | SCCS | Scientific Committee on Consumer Safety |
| EFSA | European Food Safety Authority | SED | systemic exposure dose |
| EVOH | ethylene vinyl alcohol | TDI | tolerable daily intake |
| GC | gas chromatography | TTC | threshold of toxicological concern |
| HDPE | high density PE | US EPA | United States Environmental Protection Agency |
| | | UV | ultra violet |
| | | XLDPE | cross linked low density PE |

(purity, stability, etc.). The absence of threshold values and standardized protocols complicates the CCI studies in the cosmetic industry. Nevertheless, CCI studies are legitimate to ensure consumer safety and product conformity and are of increasing interest in this field (Charron et al., 2018).

More than 30% of worldwide plastic production is used for disposable packagings (Thompson et al., 2009). Plastics are the choice materials for packagings because of their ease of use, lightness and low cost. There are more than 30 different plastics used as packaging materials. Moreover, additives are added to plastics to give them specific properties such as greater softness, flexibility or resistance (Bradley and Coulier, 2007; Cao, 2008; Thompson et al., 2009). Additives can be, among others, plasticizers, UV absorbers, antioxidants, dyes or lubricants (Bi et al., 2013; García Ibarra et al., 2018; Lau and Wong, 2000). Because they are not chemically bound to the polymer, they can migrate from the container to the content (Fasano et al., 2012; Gimeno et al., 2012; Hahladakis et al., 2018) and are consequently considered as potential leachables.

Leaching consists of the migration of a compound from the container to its content in normal conditions (leachables) of use or in extreme conditions (extractables). Thus, leachables and extractables can be additives but also non intentionally added substances (NIAS) (Bignardi et al., 2017; Muncke, 2011). NIAS are compounds that are present in a packaging material but do not have been added for a technical reason. They can be impurities, degradation products or also environmental contaminants (Bach et al., 2012; Lau and Wong, 2000; Nerin et al., 2013).

CCI studies are carried out to monitor leachables and represent important challenges for industries. Trace levels of leachables in complex matrices present a first difficulty in their evaluation. Diesters of 1,2 benzenedicarboxylic acid, commonly known as phthalates, are man made substances mostly used as plasticizers in plastic materials in order to improve their flexibility (Meeker et al., 2009; Net et al., 2015). They can also be found as impurities in raw materials and can so be considered as NIAS. Used since the 1920s (Net et al., 2015), they have recently come under the spotlight because of their potential hazards and suspected toxicological risks to human health. Indeed, studies have proved that some were endocrine disruptors and/or CMR chemicals (Fabjan et al., 2006; Meeker et al., 2009). Bisphenol A (2,2' bis(4

hydroxyphenyl)propane) is also known to be an endocrine disruptor and is used predominantly as a starting material to make plastics (Careghini et al., 2015). In Europe, it is prohibited in cosmetic products (European Parliament and Council of the European Union, 2009) and limited in food products (European Commission, 2018, p. 213). Diethyl thiodipropionate is also restricted in Regulation CE N°10/2011 concerning plastic materials intended to come into contact with food; and identified as the seventeenth plastic additive of European Pharmacopoeia (Council of Europe and European Directorate for the Quality of Medicines & HealthCare (EDQM), 2010).

Measuring trace levels of contaminants is a real challenge for analysts, because of the need to attain very low detection and/or quantification limits (In the order of µg/L or mg/L). Therefore, gas chromatography mass spectrometry (GC MS) is often used in CCI studies for its sensitivity, in food (Amiridou and Voutsas, 2011; Cacho et al., 2012; Casajuana and Lacorte, 2004; Fasano et al., 2012; Fierens et al., 2012; Guo et al., 2012), pharmaceutical (Gimeno et al., 2014; Jenke et al., 2013; Pan et al., 2008; Roberts et al., 2016) and cosmetic (Chen et al., 2005; Gimeno et al., 2012; Guo and Kannan, 2013; Shen et al., 2007; Thomas et al., 2014) studies. Liquid chromatography is also used, whether it is with UV, fluorescence (Cirillo et al., 2015; Feng and Jiang, 2012; Jenke et al., 2013; Viñas et al., 2015) or mass spectrometric detection (Ferrer et al., 2011; Lateef, 2016; Viñas et al., 2015; Zhang et al., 2016).

Toxicological evaluations are quite complex in the cosmetic industry because of the prohibition of tests on animals since 2009. Plastic materials can contain potentially dangerous substances, such as additives, monomers or NIAS, and toxicologists are responsible for the packaging risk evaluation according to Regulation CE N°1223/2009. Adapted strategies must be developed to overcome these risks and to highlight the importance of controlling cosmetic packagings and their potential contaminants.

Food packagings are prone to leach different types of contaminants depending on the type of food they contain, the temperature, the time of contact; the conditioning surface/volume ratio ... In order to avoid the difficulty of analyzing food directly, strategies using simulants have been developed (Bi et al., 2013; Cacho et al., 2012; Fasano et al., 2012) and are listed in the EC 10/2011 ((European Commission, 2011)). Simulants consist of simple matrices such as water, ethanol, olive oil or

alternative simulants and are mimicking the food behavior inside the container. They are easier to analyze, often after an extraction step. In the pharmaceutical industry, simulants can be used too (Jenke et al., 2005; Roberts et al., 2016) but case by case studies are often made on each packaging/product couple (Zhang et al., 2016).

The aim of this work was to study selected NIAS based on a pre established list of potential toxic risks. Inspired by food and pharmaceutical works, a case study is presented in which 11 potential cosmetic packagings are evaluated and their leachables analyzed using a GC MS method developed to screen for 10 phthalates (including 9 that are regulated in Europe: benzylbutyl phthalate (BBP), di *n* butylphthalate (DnBP), diethylhexyl phthalate (DEHP), diisobutyl phthalate (DiBP), bis(2 methoxyethyl) phthalate (DMEP), di *n* pentyl phthalate (DnPP), dihexyl phthalate (DHP), diisopentyl phthalate (DiPP) and *n* pentyl isopentyl phthalate (PiPP)), bisphenol A and distearyl thiodipropionate (European Pharmacopoeia plastic additive 17) which is regulated by the Regulation CE n°10/2011 (European Commission, 2011). All of these substances are of particular toxicological concern (Thompson et al., 2009).

2. Materials and methods

2.1. Selected packagings

Eleven common cosmetic packagings made up of polyethylene terephthalate (PET), polyethylene (PE), polypropylene (PP) and styrene acrylonitrile copolymer (SAN) were selected from different European suppliers. For three materials (100% PET, 100% PP and COEX 70% PEBDL/30% PEBDR), two sources of packagings were purchased in order to compare the differences between packagings made up of the same materials but originating from different suppliers.

Descriptions of each item are given in Table 1. The surface in contact with the product is calculated according to the shape. This surface corresponds to the surface in contact with the cosmetic formula in a marketed product (*i.e.* at the filling volume indicated in Table 1).

2.2. Chemicals and reagents

For reference standards, benzylbutyl phthalate (BBP, 98%), di *n* butylphthalate (DnBP, 99%), diethylhexyl phthalate (DEHP, 99.7%), diethyl phthalate (DEP, 99.5%), diisobutyl phthalate (DiBP, 99%), bis (2 methoxyethyl) phthalate (DMEP, 98.9%), di *n* pentyl phthalate (DnPP, ≥99.0%), dihexyl phthalate (DHP, ≥99.0%), bisphenol A (BPA, ≥99%), distearyl thiodipropionate (ADD17, European Pharmacopoeia Reference Standard) and 4,4' dibromobiphenyl (98%) were purchased from Sigma Aldrich (St. Quentin Fallavier, France).

Diisopentyl phthalate (DiPP, 98%) and *n* pentyl isopentyl phthalate (PiPP, 99.0% mixed of isomers) were obtained from Euromedex (Souffelweyersheim, France). *n* Octadecane (≥99.0%) and absolute ethanol came from VWR (Fontenay sous Bois, France) and heptane (99%) from Carlo Erba (Val de Reuil, France).

For simulants, ethanol (96%) was purchased from Cristalco (Chateaubriand, France). Citric acid (≥99.5%) was purchased from Sigma Aldrich (St. Quentin Fallavier, France). Disodium hydrogen phosphate dihydrate (≥99.5%) and sodium hydroxide (1M) were obtained from VWR (Fontenay sous Bois, France). Purified water was obtained from a Merck Millipore Milli Q system (Millipore, Bedford, MA, USA). Physical chemical properties, toxicological and regulatory information and the intended use of the studied substances are described in Table 2.

2.3. Migration tests

In the food industry, different simulants are used to mimic contact with different foods. For example, vegetable oil is used to simulate lipophilic products, and acetic acid 3% (w/v) hydrophilic foods (European Commission, 2011). This strategy may also be used for cosmetic studies with an adaptation of the simulants used to mimic cosmetic products. The aim of this method is to define representative simulants capable of creating “worse case” situations. A large number of cosmetics are oil in water emulsions. In these products, the continuous phase exposed to migration is predominantly aqueous. Therefore, water is a useful simulant for cosmetics. In order to be more accurate, three types of water were used: acidic, neutral and alkaline. Acidic water was prepared with citric acid and disodium hydrogen phosphate dihydrate (pH ≈ 4). Alkaline water was prepared with sodium hydroxide solution (pH ≈ 11). Demineralized water was used as the neutral water simulant (pH ≈ 7).

Cosmetic products can also contain alcohol. It is often the case with acne, hair fixative or fine fragrance products. To simulate these categories of products, ethanol was used at two different concentrations: 96% for products with a high concentration in alcohol and 30% for products with a lower concentration. 96% Ethanol was chosen on the basis of previous experiments performed in the laboratory that showed a higher tendency of most of the studied compounds to migrate to it. Ethanol 30% was also studied in order to control the action of the combination water/ethanol in proportion closer to real cosmetic products.











Studied packagings were filled with the different simulants. Volumes were measured with glass measuring cylinders. The bottles were closed by screwing or clipping their respective caps whereas tubes were filled by the top and thermally sealed.

Table 1
Selected packagings and their description.

| Code | Material | Appearance | Volume (mL) | Shape and type | Closing system | Theoretical surface in contact with the cosmetic product (cm ²) | Surface/volume ratio |
|------|--------------------------------|---------------------|-------------|--------------------|----------------|---|----------------------|
| P11 | 100% PET | Clear, colorless | 100 | Elliptical bottle | Cap | 124 | 0.91 |
| P12 | 100% PET | Clear, colorless | 100 | Cylindrical bottle | Cap | 115 | 0.90 |
| P13 | 50% PET/50% rPET | Clear, light yellow | 200 | Elliptical bottle | Cap | 209 | 0.90 |
| P14 | 100% PP | Opaque, white | 500 | Elliptical bottle | Pump | 362 | 0.89 |
| P15 | 100% PP | Opaque, dark green | 600 | Cylindrical bottle | Pump | 396 | 0.86 |
| P16 | 100% SAN | Opaque, white | 15 | Cylindrical bottle | Pump | 63 | 1 |
| P17 | 100% HDPE | Opaque, white | 100 | Cylindrical bottle | Cap | 112 | 0.89 |
| P18 | 70% LLDPE/30% XLDPE | Opaque, white | 40 | Cylindrical tube | Cap | 60 | 1 |
| P19 | COEX 70% LLDPE/30% XLDPE//EVOH | Opaque, white | 50 | Cylindrical tube | Cap | 61 | 1 |
| P110 | COEX 70% LLDPE/30% XLDPE//EVOH | Opaque, white | 50 | Cylindrical tube | Cap | 66 | 1 |
| P111 | 70% HDPE/30% LLDPE | Opaque, white | 40 | Cylindrical tube | Cap | 59 | 1 |



PI: packaging item; rPET: recycled PET; HDPE: high density PE; LLDPE: low linear density PE; XLDPE: cross-linked low-density PE; COEX: coextruded; EVOH: Ethylene vinyl alcohol.

Table 2
Physico-chemical characteristics of targeted compounds.

| Compound | Abbreviation | CAS number | Molar mass (g/mol) | Structure | Solubility | Boiling point (Physical state) | Toxicological risk ^a | Use | European legislation | m/z ratios (Stock solution n°) |
|-------------------------------|--------------|-------------|--------------------|---|-------------------------|--------------------------------|---|---|--|--------------------------------|
| Benzylbutyl phthalate | BBP | 85-68-7 | 312.37 |  Water: 2.69 mg/L (25 °C) (1) Soluble in ethanol (2) | 370 °C (1) (L) | R1B Endocrine disruptor | Plasticizer (softener) of PVC or other polymers, in sealants, adhesives, paints, inks and lacquers (3) | CE n°10/2011: SML = 30 mg/kg + restrictions CE n°1223/2009: prohibited | 91; 104; 149; 150; 206 (solution n°2) | |
| Di-n-butyl phthalate | DnBP | 84-74-2 | 278.35 |  Water: 11.2 mg/L (25 °C) (1) Very soluble in alcohol (4) | 340 °C (1) (L) | R1B Endocrine disruptor | Plasticizer, solvent for oil-soluble dyes, insecticides and other organics, antifouling agent, textile fiber lubricant, fragrance fixative, insect repellent (4) | CE n°10/2011: SML = 0.3 mg/kg + restrictions CE n°1223/2009: prohibited | 104; 149; 150; 205; 223 (solution n°2) | |
| Diethylhexyl phthalate | DEHP | 117-81-7 | 390.57 |  Water: 0.34 mg/L (25 °C) (1) Soluble in ethanol (2) | 384 °C (1) (L) | R1B Endocrine disruptor | Plasticizer in PVC applications and flexible vinyls (4) | CE n°10/2011: SML = 1.5 mg/kg + restrictions CE n°1223/2009: prohibited | 71; 149; 150; 167; 279 (solution n°1) | |
| Diethyl phthalate | DEP | 84-66-2 | 222.24 |  Water: 1080 mg/L (25 °C) (1) Miscible with alcohol (4) | 295 °C (1) (L) | Endocrine disruptor | Manufacturing celluloid, solvent for cellulose acetate in manufacturing varnishes and dopes, denaturing alcohol, vehicle for fragrance and cosmetic ingredients (4) | - | 76; 105; 149; 150; 177 (solution n°2) | |
| Di-isobutyl phthalate | DIBP | 84-69-5 | 278.35 |  Water: 20.3 mg/L (20 °C) (1) Soluble in ethanol (2) | 297 °C (1) (L) | R1B | Plasticizer for nitrocellulose, cellulose ether, polyacrylate and polyacetate dispersions. Gelling aid in combination with other plasticizers used for plastic, lacquers, adhesives, explosive material and nail polish (5) | Absent from CE n°10/2011: prohibited CE n°1223/2009: prohibited | 76; 104; 149; 150; 167; 223 (solution n°1) | |
| Diisopentyl phthalate | DIPP | 605-50-5 | 306.40 |  Insoluble in water (4) Very soluble in ethanol (6) | 339 °C (7) (L) | R1B | Plasticizer for nitrocellulose and resin lacquers, preventing foam in manufacturing of glue, in rubber cements (8) | CE n°1223/2009: prohibited | 71; 104; 149; 237 (solution n°2) | |
| Bis(2-methoxyethyl) phthalate | DMEP | 117-82-8 | 282.30 |  Water: 8500 mg/L (25 °C) (1) Soluble in ethanol (2) | 340 °C (1) (L) | R1B | Plasticizer in the production of nitrocellulose, acetyl cellulose, polyvinyl acetate, polyvinyl chloride and polyvinylidene chloride. Solvent, enameled wire, film, high-strength varnish and adhesive, in pesticides (8) | CE n°1223/2009: prohibited | 59; 104; 149; 207; 281 (solution n°1) | |
| Di-n-pentyl phthalate | DnPP | 131-18-0 | 306.41 |  Water: 0.189 mg/L (25 °C) (1) Soluble in ethanol (2) | 342 °C (9) (L) | R1B | Plasticizer in polyvinyl chloride (9) | Absent from CE n°10/2011: prohibited (10) CE n°1223/2009: prohibited | 104; 149; 150; 207; 237 (solution n°2) | |
| N-pentyl isopentyl phthalate | PIPP | 776297-69-9 | 306.41 |  Water: no available data Soluble in ethanol (11) | 371 °C ^c (L) | R1B | Plasticizer in plastic material (12) | CE n°1223/2009: prohibited | 71; 149; 219; 237 (solution n°1) | |
| Dihexyl phthalate | DHP | 84-75-3 | 334.46 |  Water: 0.24 mg/L (20 °C) (1) (L) | 210 °C (5 mmHg) (6) (L) | R1B Endocrine disruptor | Plasticizer for cellulose and vinyl plastics (13) | Absent from CE n°10/2011: prohibited (10) | 149; 207; 233; 251; 281 (solution n°1) | |

(continued on next page)

Table 2 (continued)

| Compound | Abbreviation | CAS number | Molar mass (g/mol) | Structure | Solubility | Boiling point (Physical state) | Toxicological risk ^a | Use | European legislation | m/z ratios (Stock solution n ^c) |
|--|--------------|------------|--------------------|---|-------------------|--------------------------------|---|---|---|---|
| Bisphénol A | BPA | 228.29 | 228.29 |  <p>Ethanol: no available data Water: 120 mg/L (25 °C) (1) Soluble in alcohol (4) Insoluble in water</p> | 220 °C (1) (5) | R2 Endocrine disruptor | Monomer used for polycarbonate and epoxy resins (4) | CE n°2018/213: SML = 0,05 mg/kg CE n°1223/2009: prohibited | 91; 119; 213; 214; 228 (solution n°2) | |
| Distearyl thiodipropionate (plastic additive n°17) | ADD17 | 683.17 | 683.17 |  <p>Ethanol: no available data Very soluble in benzene and olefin polymers (14)</p> | MP: 61 °C (6) (S) | – | Plastic additive (15) | CE n°10/2011: SML(t) = 5 mg/kg European Pharmacopoeia | 106; 111; 125; 139; 178; 325 (solution n°2) | |

References: (1) (Howard and Chemical Rubber Company, 1997); (2) (AFNOR, 2014); (3) (European Chemicals Agency, 2010); (4) (O'Neil and Merck and Co, 2006); (5) (European Chemicals Agency, 2009); (6) (Haynes, 2014); (7) (Environment Agency Austria, 2012); (8) (Federal Institute for Occupational Safety and Health, 2011); (9) (Bureau for Chemical Substances, 2013); (10) (Agence nationale de sécurité sanitaire alimentation, environnement, travail, 2015); (11) (Gimeno et al., 2014); (12) (Federal Institute for Occupational Safety and Health, 2012); (13) (Federal Institute for Occupational Safety and Health, 2013); (14) (Larrañaga et al., 2016); (15) (Council of Europe and European Directorate for the Quality of Medicines & HealthCare (EDQM), 2010).

^a Globally Harmonized System of Classification and Labelling of Chemicals (GHS).

^b Data generated by CS ChemProp L: Liquid/S: Solid at atmospheric pressure and ambient temperature; Pressure not specified = atmospheric pressure.

The migration tests strategy is described on Fig. 1. Inert glass containers were used to stock simulants considered as control samples. One was kept at 4 °C and the other in a climatic chamber at 50 °C, in order to verify the effect of heat on the matrices. Moreover, these control samples were used to prove that no contamination had occurred during preparation, emptying and storage steps. This experimental condition permitted an accelerated aging process of the products. Packagings were emptied after storage under accelerated conditions (50 °C/1 month) and kept at 4 °C in order to be sure that the migration is stopped.

55 sets (packaging/simulant) were studied in duplicate. Moreover, 10 blanks were prepared, with 120 samples in total.

Before analysis, simulants in inert glass containers were removed from the refrigerator and left to come to room temperature, before being transferred to chromatographic vials.

2.4. Analytical procedure

All analyses were performed on an Agilent 7890A gas chromatography system coupled with an Agilent 5975C inert XL MSD with quadripole (Les Ulis, France) equipped with an electron impact ionization source and a Gerstel MPS 2 autosampler. A HP 5MS capillary column (30 m length, 0.25 mm, 0.25 µm film thickness) was used for separation. The temperature of the injector was set to 280 °C. Injection volumes varied depending on the matrix: 1.0 µL was injected for 96% ethanol, 0.8 µL for 30% ethanol and 0.5 µL for aqueous samples. Injection was in split mode (ratio 2:1). Helium was used as a carrier gas at a constant flow of 1 mL/min. The temperature gradient began at 100 °C and was raised to 200 °C at 30 °C/min. Then, the temperature was increased to 280 °C at 5 °C/min and continued at 50 °C/min, until 320 °C (held for 5 min). The temperature of the transfer line and ion

source were 250 °C and 230 °C, respectively. The electron impact energy was 70 eV. The compounds were detected in selected ion monitoring (SIM) mode according to m/z ratios presented in Table 2. Dwell time is 50 ms for all compounds except for DMEP and DiPP (25 ms) because 4,4' dibromobiphenyl is detected in the same m/z window.

Concentration thresholds were determined using regulations (European Commission, 2011; 2018; European Parliament and Council of the European Union, 2009, p. 200), internal data and systemic exposure dose (SED) calculation. The concentration thresholds defined are: 0.5 mg/kg for phthalates, 0.05 mg/kg for BPA and 5.0 mg/kg for ADD17. The analytical method development must therefore attain an LOQ at these values for the corresponding compounds.

Internal standards (IS) are 4,4' dibromobiphenyl for phthalates, as indicated in the AFNOR norm NF EN 16521 (AFNOR, 2014), and for BPA, since the molecular structures are similar, and *n* octadecane for ADD17. Individual phthalates, BPA and IS solutions were individually prepared by weighing 10 mg of each compound in 10 mL of absolute ethanol. ADD17 was prepared at the same concentration but with heptane as the dilution solvent. Solid compounds in solvent were placed in an ultrasonic bath for 10 min until complete dissolution. Compounds were separated into two stock solutions (Table 2) in order to avoid too many m/z zones on the same chromatograms and to allow better detection of the peaks. Diluted solutions were prepared to obtain calibration curves for each compound. Dilution solvent varied as a function of the matrix: demineralized water for aqueous simulants; 30% ethanol for 30% ethanol simulant and absolute ethanol for 96% ethanol. 4,4' dibromobiphenyl and *n* octadecane stock solutions were added to each solution to obtain final IS concentrations of 500 µg/L and 200 µg/L respectively.

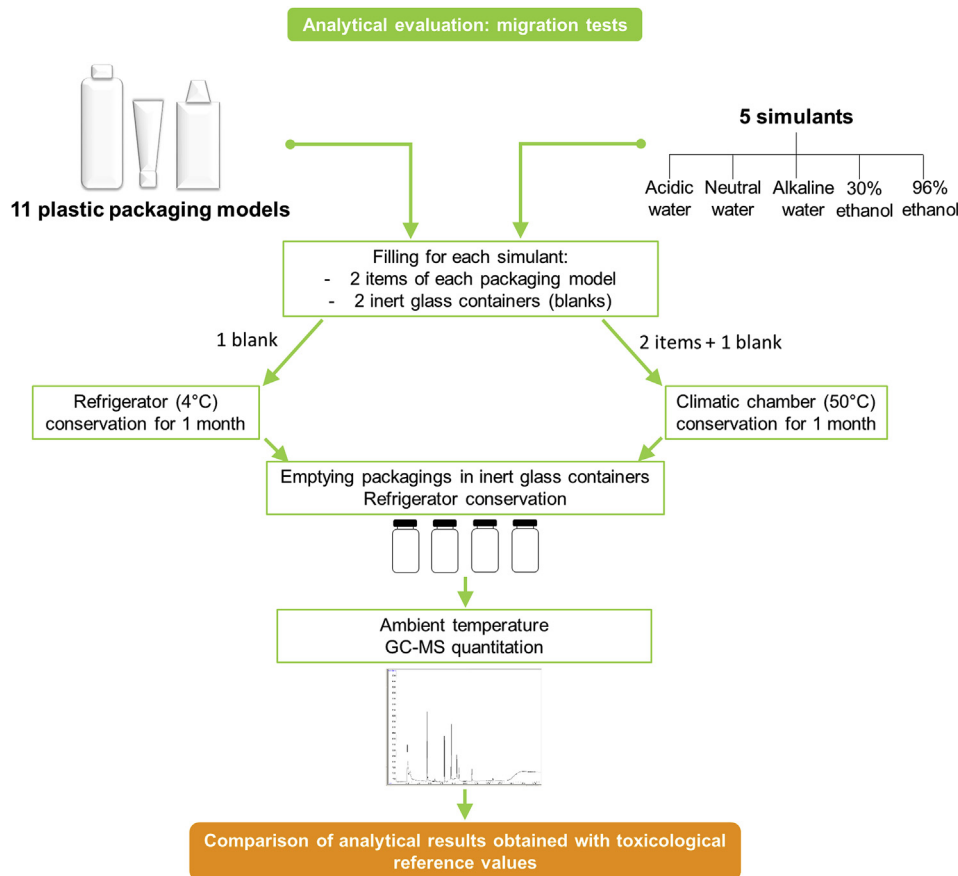


Fig. 1. Workflow of the strategy for migration studies.

2.5. Method validation

LOQs were determined by injecting the lowest concentration solution (in ethanol and in water) until a signal to noise ratio of at least 10:1 was obtained for each compound. LODs are considered to be LOQs/3. Linearity was determined by injecting solutions at eight different concentrations from the LOQ. Repeatability is evaluated by injecting six times a solution containing contaminants at the selected concentration threshold. Accuracy is determined by analyzing blanks of absolute ethanol and water spiked at two different levels in triplicate (the selected concentration threshold and twice this value). The recovery is calculated based on Equation (1).

$$\text{Recovery (\%)} = \frac{\bar{y}_{\text{exp}}}{y_{\text{theo}}} \cdot 100 \quad (1)$$

Where \bar{y}_{exp} is an experimental area value obtained by calculating the average of the ratio between compound and internal standard peak areas of 3 replicates. y_{theo} is a theoretical area value obtained from the calibration curve equation, with the concentration of the spiked

solutions.

The precision of analysis was estimated by calculating the relative standard deviation of the 3 replicates of spiked samples.

Laboratory control samples (one for each simulant), were analyzed with each set of samples to examine background contamination. A full set of calibration standards was analyzed before each set of samples and control standards were injected during the sets in order ensure system stability. Before each injection set, solvent blank (absolute ethanol, water or 30% ethanol) were injected to ensure the absence of peaks at the retention times of the studied compounds.

In order to confirm that no contamination occurred, control samples were analyzed. If one of the target compounds was detected in a control sample, the control sample peak area was subtracted from the sample peak area.

Validation was performed in absolute ethanol and neutral demineralized water. Parameters were also verified in ethanol 30% in order to be sure that the method is valid in that simulant too.

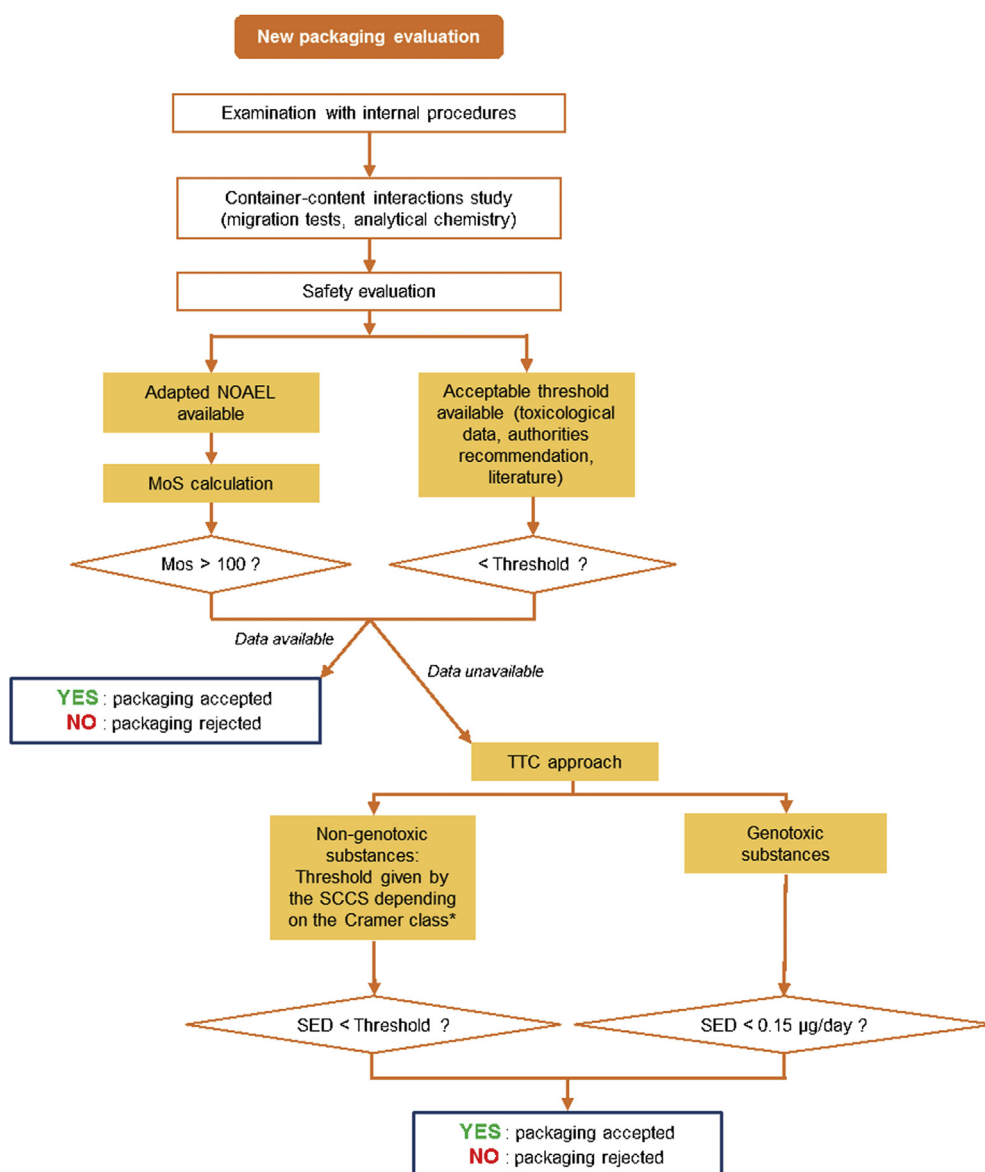


Fig. 2. Workflow of the toxicological evaluation strategy; NOAEL: no observed adverse effect level; MoS: margin of safety; TTC: threshold of toxicological concern; SCCS: Scientific Committee on Consumer Safety; SED: systemic exposure dose. Some other considerations must be taken depending on chemical specificity and according to the TTC concept (i.e. organophosphates, carbamates, metals ...).

2.6. Toxicological procedure and analysis

The toxicological strategy offers four options for the safety evaluation of different packagings.

Materials and analytical researches combined with toxicological approach were performed to guarantee the compatibility between the container and its content and consequently consumer safety (Fig. 2).

For this purpose, several toxicological values were used: The Tolerable Daily Intake (TDI), the Reference Dose (RfD) and the Derived no Effect Level (DNEL). The TDI is the estimated concentration of a substance which can be ingested daily over a lifetime without significant risks to human health. TDIs are set out by the EFSA (European Food Safety Authority) and are based on selected and appropriate studies. The RfD set out by the US EPA is defined as “an estimate” (with some uncertainties) of a daily exposure to the human population (including sensitive subgroups) that is likely to be without an appreciable risk of deleterious effects during a lifetime. Finally, the DNEL (oral or dermal) is defined as the level of exposure to a substance above which humans should not be exposed. All of these values were derived from NOAEL, LOAEL or benchmark dose (BMD) with uncertainty factor for reflection of limited data if necessary. The discrepancies between these different values are due to the fact that US EPA, EFSA and REACH use point of departure values based on different studies, different endpoints and/or different scenarios. As previously explained, different values furthermore arise depending on whether NOAEL, LOAEL or BMD are used, and which safety or uncertainty factors are applied.

Exposure assessment of phthalates was performed using the following information and by considering the worst case scenario. For this purpose, we considered a total amount of product applied each day equal to 18 g (according to the last version of the SCCS guidance notes (Scientific Committee on Consumer Safety, 2015)), a total bioavailability equivalent to 100%, a body weight of 60 kg for an adult and only the highest detected concentrations were used for the systemic exposure calculation of each impurity.

3. Results and discussion

3.1. Method performance

The validation parameters are summarized in Table 3. For studied compounds (except ADD17), LOD and LOQ were 2 and 5 µg/L for DEHP and DiBP respectively; 67 and 200 µg/L for DMEP respectively in ethanolic samples. ADD17 values determined only in ethanolic samples were 1333 and 4000 µg/L respectively. In water samples, LOD and LOQ were 2 and 5 µg/L for DiBP to 167 and 500 µg/L for DMEP. These values are comparable to those reported in the literature (Bi et al., 2013; Ferrer et al., 2011; Gimeno et al., 2012; Thomas et al., 2014). Even if there were no pre concentration steps, LOQ were always smaller than the selected concentration threshold and consequently, the protocol is adapted to the study.

A large linearity ranging from the LOQ to 1000 µg/L was observed for each target compound (to 15000 µg/L for ADD17). Correlation coefficients were greater than 0.990 as recommended by the standardization ISO 12787 (AFNOR, 2011). Repeatability was less than 8% RSD except for ADD17 (13%). The spiking recoveries varied between 90% and 114% for water samples and between 85% and 108% for ethanolic samples (96%) and were reproducible as demonstrated by the RSD values which were lower than 10%.

Validation parameters in 30% ethanol were considered as acceptable and are available as supplementary data.

Fig. 3 shows examples of GC MS chromatograms: (a) a blank of absolute ethanol, (b) a standard solution n°1 in absolute ethanol at the selected concentration threshold and (c) a sample of simulant 96% ethanol after one month in P18 (70% LLDPE/30% XLDPE).

Table 3
Overview of the method performance characteristics.

| Compound | Linear range (µg/L) | Linearity R ² | Repeatability %RSD | | Accuracy | | Spiked at concentration threshold | | Spiked at twice concentration threshold | | LOQ (µg/L) (in water if different) | LOD (µg/L) (in water if different) | | | |
|------------|---------------------|--------------------------|--------------------|----------|--------------|----------|-----------------------------------|----------|---|----------|---------------------------------------|---------------------------------------|------------|----------|--------|
| | | | In ethanol | In water | In ethanol | In water | In ethanol | In water | In ethanol | In water | | | | | |
| | | | Recovery (%) | %RSD | Recovery (%) | %RSD | Recovery (%) | %RSD | Recovery (%) | %RSD | | | | | |
| Phthalates | BBP | 20–1000 | 0.991 | 0.995 | 3.2 | 3.8 | 86 | 2.8 | 112 | 11.5 | 90 | 4.6 | 5.2 | 20 | 7 |
| | DnBP | 10–1000 | 0.996 | 0.998 | 1.4 | 3.6 | 88 | 2.5 | 107 | 3.8 | 96 | 0.7 | 2.4 | 10 | 3 |
| | DEHP | 5–1000 | 0.991 | 0.996 | 2.2 | 4.6 | 90 | 0.9 | 90 | 3.0 | 94 | 1.8 | 2.6 | 5 (15) | 2 (5) |
| | DEP | 10–1000 | 0.999 | 0.995 | 1.4 | 5.4 | 92 | 2.0 | 94 | 3.0 | 98 | 0.8 | 1.0 | 10 | 3 |
| | DiBP | 5–1000 | 0.998 | 0.998 | 0.7 | 3.2 | 96 | 2.4 | 96 | 3.0 | 99 | 3.9 | 0.7 | 5 | 2 |
| | DnPP | 10–1000 | 0.993 | 0.991 | 2.8 | 4.9 | 85 | 3.8 | 104 | 6.0 | 96 | 1.4 | 9.9 | 10 (50) | 3 (17) |
| DMEP | 20–1000 | 0.992 | 0.991 | 1.3 | 6.0 | 85 | 1.7 | 98 | 5.2 | 92 | 0.9 | 2.9 | 200 (5000) | 67 (167) | |
| | 10–1000 | 0.990 | 0.993 | 2.3 | 5.7 | 85 | 2.0 | 105 | 10.1 | 96 | 1.9 | 13.40 | 20 (30) | 7 (10) | |
| | 30–1000 | 0.995 | 0.990 | 2.5 | 7.4 | 92 | 2.2 | 114 | 3.6 | 98 | 1.2 | 1.9 | 10 (30) | 3 (10) | |
| DHP | 10–1000 | 0.993 | 0.991 | 3.6 | 5.8 | 86 | 2.6 | 104 | 4.0 | 93 | 0.9 | 2.2 | 30 (80) | 10 (27) | |
| | 10–1000 | 0.991 | 0.997 | 5.2 | 6.7 | 96 | 0.5 | 108 | 6.8 | 107 | 0.8 | 3.7 | 10 | 3 | |
| BPA | 4000–15000 | 0.991 | – | 12.7 | – | 88 | 24.3 | – | – | 108 | 3.6 | – | 4000 | 1333 | |

NB: there are no results for ADD17 in water because this compound is in solution in heptane, which is not soluble in water.

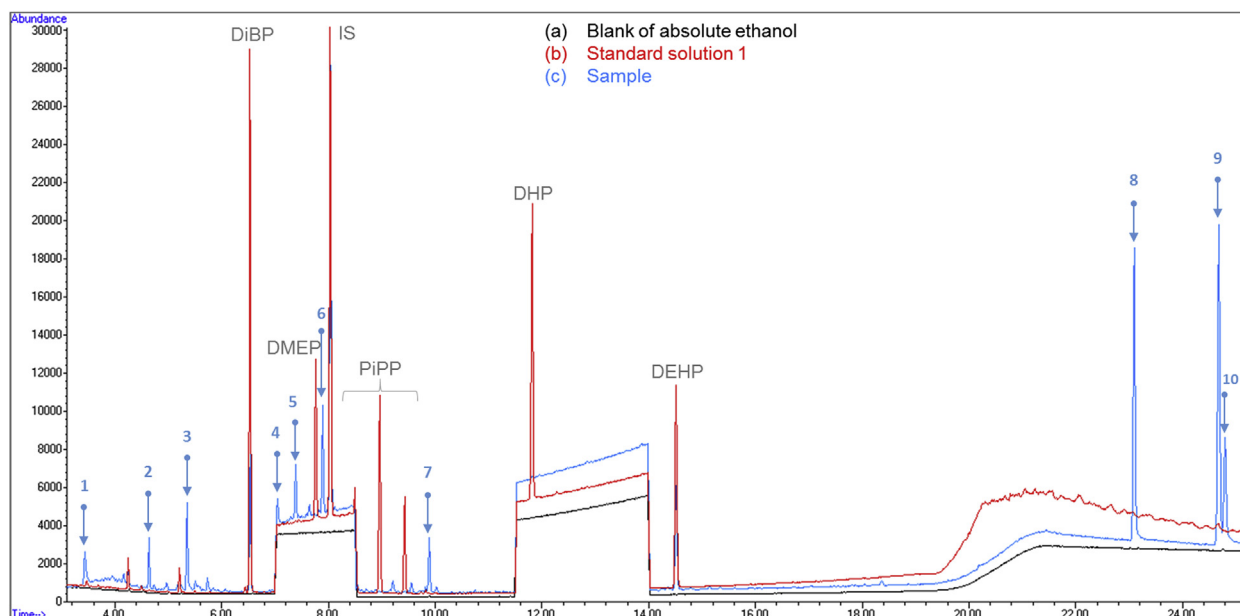


Fig. 3. GC-MS chromatograms in SIM mode obtained from (a) a blank of absolute ethanol, (b) standard solution n°1 in absolute ethanol at selected *concentration* threshold (400 µg/L) and (c) a sample of simulant 96% ethanol after one month in PI8 (70% LLDPE/30% XLDPE) at 50 °C with IS at 500 µg/L. The blue arrows indicate 10 unknown peaks i.e. peaks that are neither phthalates studied nor BPA, ADD17 or IS. The profile in “tread of a stair” is due to evolution of *m/z* during the analysis. (For interpretation of the references to color in this figure legend, the reader is referred to the Web version of this article.)

3.2. Migration results

Fig. 4 highlights how many compounds over the 12 studied were detected in each tested packaging. As can be seen on this graph, there are more contaminants detected in PI4 to PI11 than in PI1 to PI3. PI8 (70% LLDPE/30% XLDPE) is actually the packaging with the highest

number of target compounds detected (6 out of the 12 studied). On the contrary, in PI3 (50% PET/50% rPET), none of the contaminants were detected (< LOD) whatever the simulant. This packaging can be considered the “cleanest” pack of this study. In several packagings (PI1, PI5, PI7, PI8, PI9, PI10), the total number of contaminants extracted corresponds to the number of contaminants extracted by simulant 96%

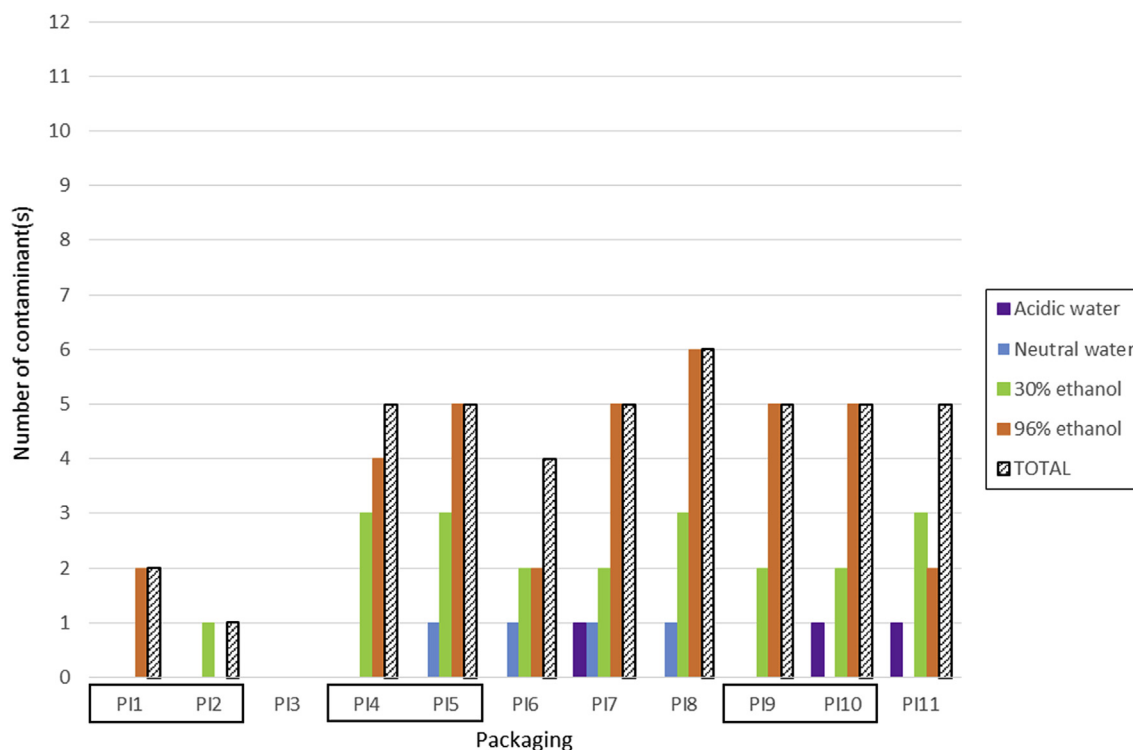


Fig. 4. Number of selected contaminant(s) detected in each packaging reviewed. NB: alkaline water is absent from this graph because none of the studied compounds was detected in this simulant. TOTAL corresponds to the sum of all the different contaminants detected in the packaging in all the simulants. Boxed texts are pairs made up of the same materials but coming from different suppliers (PI1 and PI2 in 100% PET; PI4 and PI5 in 100% PP; PI9 and PI10 in COEX 70% LLDPE/30% XLDPE//EVOH).

ethanol. This is not the case for the other packagings which demonstrate specific behavior versus the simulant type. Both ethanol simulants extracted in 10 packs out of 11, proving that ethanol has the strongest extraction potential of the simulants tested.

Fig. 5 presents the nature of the contaminants detected in each packaging as a function of the simulants used. Five compounds: ADD17, PiPP, DnPP, DMEP and DEHP were not detected at all. Moreover, none of the compounds studied were detected in alkaline water.

An analytical issue occurred during the detection of DEP in acidic water. Actually, at the retention time of DEP, acidic water chromatograms were much disrupted (chromatogram available in supplementary data). Because of this phenomenon, it was not possible to detect DEP in this simulant below 300 µg/L. This concentration is below the selected concentration threshold and this issue was considered as acceptable. Consequently, this contaminant is not represented on Fig. 5a.

DiBP was the only contaminant detected in acidic water (Fig. 5a). Its concentration varied from below the LOQ in packagings P17 (100% HDPE) and P110 (COEX 70% LLDPE/30% XLDPE//EVOH) to 20 µg/L in P11 (70%HDPE/30%LLDPE). This contaminant was detected in only these 3 packagings. In neutral water (Fig. 5b), as in acidic water, only one compound was detected: DEP. It was present in 5 packagings over the 11 studied. The maximum concentration observed was in P17 (100% HDPE). The contaminants detected in these two simulants are not the same. This observation can be explained by the fact that the concentrations measured were relatively low (close to the LOD/LOQ). Moreover, no data was found on the effect of pH on the solubility of phthalates. It is noticed that none of the compounds studied were observed in packagings P11 to P14 and P19 for the water simulants. The concentrations of DEP and DiBP measured were more than thirty times lower than in 96% ethanol.

In ethanol 30% and 96%, extraction rates were higher, both in terms of the concentrations and number of contaminants detected. In 30% ethanol (Fig. 5c), 4 compounds were extracted. DEP and DnBP were the most frequently extracted compounds detected in 9 packagings out of 11. Their maximum concentrations were measured at 40 µg/L and 7 µg/L respectively. The total concentration varied from below the LOD to

54 µg/L for P18. This last packaging was the most contaminated, but even with the sum of all compounds, the total concentration is still under the selected concentration threshold of 500 µg/L in this simulant. The higher concentrations were observed with 96% ethanol, in which the sum of the contaminants reached a concentration of 681 µg/L in P18. BBP and DEHP were the principal compounds extracted. The selected concentration threshold is 400 µg/L in 96% ethanol. The total concentration of contaminants extracted from P16 and P18 is above this threshold.

Migration results are exposed in Table 4. Numerical values are given when compounds were detected at a concentration higher than their LOQ. Among the 65 detections, only 35 were above the LOQ. Only DiBP was detected above its selected concentration threshold (500 µg/L in the three water simulants and 30% ethanol; 400 µg/L in 96% ethanol). 491 µg/L (equal to 0.6 ppm) of this contaminant was found in the simulant 96% ethanol contained in the packaging in 100% SAN (P16). A toxicological evaluation is therefore required in order to determine if this concentration of DiBP presents a risk for consumer safety. DEP was the most detected contaminant, being present in 16 samples. DnBP and DiBP were also found in at least 10 samples.

Comparing the packagings made up of the same materials but coming from different suppliers (P11 vs 2, P14 vs 5 and P19 vs 10), the contamination profiles were not exactly the same. Even if the 100% PET packagings (P11 and P12) did not leach the same compounds in the same simulants, they leached very few and very low concentrations of contaminants. On the contrary, P14 and P15, the 100% PP packagings leached far more contaminants as with P19 and P110 (COEX 70% LLDPE/30% XLLDPE//EVOH). These differences can probably be explained by differences in the quality of the raw materials chosen by suppliers.

This study focused on 12 selected compounds of toxicological interest but also highlighted 10 unidentified compounds (named “unknown peaks 1 to 10” on the chromatogram presented on Fig. 3.) These compounds should be identified to evaluate their toxicological potential and risk for consumers. Although the selected ion monitoring acquisition mode is not dedicated to the identification of molecules, some

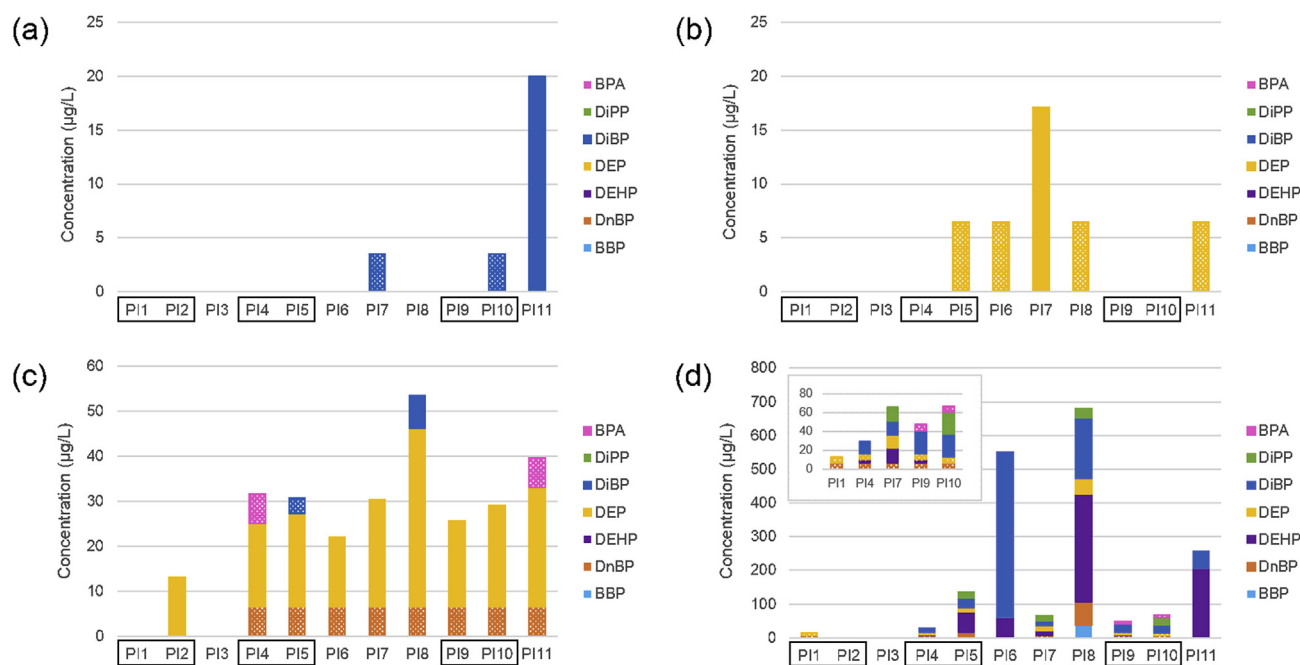


Fig. 5. Total concentration of studied contaminants in each packaging reviewed in (a) acidic water, (b) neutral water, (c) 30% ethanol and (d) 96% ethanol. NB: there is no graph for alkaline water because no target compounds were detected in this simulant. Bars with dots corresponds to concentrations between LOD and LOQ; values for these concentrations were calculated as following: $LOD + LOQ/2$. Boxed texts are pairs made up of the same materials but coming from different suppliers (P11 and P12 in 100% PET; P14 and P15 in 100% PP; P19 and P110 in COEX 70% LLDPE/30% XLDPE//EVOH). DEP concentration in acidic water (a) is not represented on graph (a) since it is not possible to detect its contaminant under 300 µg/L.

Table 4
Migration tests results in the 5 simulants studied in µg/L.

| Simulants | Contaminants | PI1 | PI2 | PI3 | PI4 | PI5 | PI6 | PI7 | PI8 | PI9 | PI10 | PI11 |
|----------------|--------------|-------------|------------|------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|
| Acidic water | Phthalates | DEP: < 300 | DEP: < 300 | DEP: < 300 | DEP: < 300 | DEP: < 300 | DEP: < 300 | DEP: < 300 | DEP: < 300 | DEP: < 300 | DEP: < 300 | DEP: < 300 |
| Neutral water | BPA | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD |
| | Phthalates | < LOD | < LOD | < LOD | < LOD | < LOD | DEP: 17.1 | < LOD | DEP: < LOQ | < LOD | < LOD | DEP: < LOQ |
| Alkaline water | BPA | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD |
| | Phthalates | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD |
| 30% Ethanol | BPA | < LOD | DEP: 13.1 | < LOD | DnBP: < LOQ | DnBP: < LOQ | DnBP: < LOQ | DnBP: < LOQ | DnBP: < LOQ | DnBP: < LOQ | DnBP: < LOQ | DnBP: < LOQ |
| | Phthalates | < LOD | DEP: 18.6 | < LOD | DEP: 20.7 | DEP: 15.5 | DEP: 23.9 | DEP: 39.8 | DEP: 39.8 | DEP: 19.2 | DEP: 22.6 | DEP: 26.6 |
| 96% Ethanol | BPA | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD |
| | Phthalates | DnBP: < LOQ | < LOD | < LOD | DnBP: 16.2 | DnBP: 59.5 | DnBP: < LOQ | DnBP: < LOQ | BBP: 37.5 | DnBP: < LOQ | DnBP: < LOQ | DEHP: 205.9 |
| BPA | Phthalates | DEP: < LOQ | < LOD | < LOD | DEHP: 59.8 | DEHP: 491.0 | DEHP: 15.6 | DEHP: 14.4 | DnBP: 69.2 | DEHP: < LOQ | DEHP: < LOQ | DEHP: 51.3 |
| | Phthalates | < LOD | < LOD | < LOD | DEP: 12.5 | DEP: 12.4 | DEP: 14.5 | DEP: 14.4 | DEHP: 320.7 | DEP: < LOQ | DEHP: 24.4 | DEHP: 24.4 |
| | Phthalates | < LOD | DEP: 12.4 | < LOD | DnBP: 30.1 | DnBP: 30.1 | DnBP: 30.1 | DnBP: 14.5 | DEP: 46.2 | DnBP: 24.2 | DnBP: 24.2 | DnBP: 53.0 |
| | Phthalates | < LOD | DEP: 17.6 | < LOD | DIPP: 17.6 | DIPP: 17.6 | DIPP: 15.0 | DIPP: 15.0 | DIPP: 180.1 | DIPP: 27.0 | DIPP: 53.0 | DIPP: 53.0 |
| ADD17 | BPA | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD |
| | Phthalates | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD | < LOD |

Table 5
Toxicological reference values of targeted compounds.

| Compound | Abbreviation | TDI (EFSA) mg/kg bw/day | RfD (US EPA) mg/kg bw/day | DNEL dermal (REACH) mg/kg bw/day | DNEL oral (REACH) mg/kg bw/day | Acidic water | Neutral water | Alkaline water | 30% Ethanol | 96% Ethanol | SED µg/kg bw/day (worst case) | Conclusion |
|------------------------|--------------|-------------------------|---------------------------|----------------------------------|--------------------------------|----------------|------------------|----------------|------------------|-------------------|-------------------------------|------------|
| Benzylbutyl phthalate | BBP | 0,5 | 0,2 | 4,5 | 0,5 | Not detected | Not detected | Not detected | Not detected | Not detected | - | acceptable |
| Di-n-butyl phthalate | DnBP | 0,01 | 0,1 | 0,07 | 0,007 | Not detected | Not detected | Not detected | < LOQ | Up to 69,2 (P18) | 0,02 | acceptable |
| Diethylhexyl phthalate | DEHP | 0,05 | 0,02 | 0,72 | 0,036 | Not detected | Not detected | Not detected | Not detected | Up to 320,7 (P18) | 0,096 | acceptable |
| Diethyl phthalate | DEP | 0,5# | 0,8 | 7,5 | 0,75 | < 300 | Up to 17,1 (P17) | Not detected | Up to 39,8 (P18) | Up to 46,2 (P18) | 0,013 | acceptable |
| Di-isobutyl phthalate | DiBP | ND | - | - | 0,008 | Up to 20 (P11) | Not detected | Not detected | Up to 7,3 (P18) | Up to 491 (P16) | 0,147 | acceptable |
| Diisopentyl phthalate | DiPP | - | - | 0,07 | 0,007 | Not detected | Not detected | Not detected | Not detected | Up to 53 (P10) | 0,016 | acceptable |

a TDI for DEP was not set by the SCF or EFSA, but the TDI of 0.5 mg/kg bw/day was proposed by the World Health Organization (Sekizawa et al., 2003), and may therefore be considered. All other toxicological reference values (TDI, RfD and DNEL) come from the websites of EFSA, US EPA and REACH respectively.

peaks are thought to be related to the phthalate family of compounds. It is well established that phthalate fragmentation under electronic impact mode forms a characteristic protonated phthalic anhydride molecular ion at m/z 149 except for dimethyl phthalate (Jeilani et al., 2011). This is the main ion detected for peaks 1, 2, 5, 8, 9 and 10 and the second one for peak 4. As for DMEP, the latter presents a main peak at 207. No information can be extracted from the mass spectra of the other unknown peaks.

3.3. Toxicological analysis of results

The results obtained were compared to the toxicological reference values (results are presented Table 5). Because the following compounds BBP, DMEP, DnPP, PiPP, DHP, BPA and ADD17 were not detected (whatever the pack and simulants used), assessment cannot be performed. For the other impurities (DnBP, DEHP, DEP, DiBP and DiPP), calculated SED were 0,02, 0,096, 0,013, 0,147 and 0,016 $\mu\text{g}/\text{kg bw}/\text{day}$ respectively: all of these values were always below the reference values used (expressed as $\text{mg}/\text{kg bw}/\text{day}$) as well as the TTC value. Moreover, it should be noted that these impurities are found preferentially with the simulant ethanol and more precisely with 96% ethanol. In view of such low exposures of these impurities found in the samples, there would be no quantifiable risk for the consumer.

4. Conclusion

Cosmetic products are used on a daily basis by adults, teenagers but also children and babies. Exposition to plastic additives through the use of hygiene or beauty products must be controlled and evaluated to ensure consumer safety.

A strategy developed to evaluate new packagings through the analysis of 12 toxicologically selected compounds were presented. This work combines analytical chemistry and toxicological evaluation and aim to be a base for developing a model applicable to all the NIAS. Eleven packagings were put in contact with 5 simulants chosen to mimic cosmetics behavior in order to reinforce the safety evaluation of the cosmetic containers. Some phthalates and BPA were detected in several simulants but without any risks for consumers. DiBP and DEHP were detected at high concentrations compared to the chosen concentration threshold. However, these quantities were proved to be safe for users.

A more exhaustive study could be led to identify other molecules of toxicological interest. Screening studies would enable an extension of the studied compounds panel.

The analytical method presented in this paper could be associated with suitable extraction techniques to extend the study to oily simulants such as liquid paraffin or glycerin. These matrices would allow to cover a larger panel of cosmetic products, since they are close to water in oil emulsions or formulas with high contents of glycerin or liquid paraffin. Moreover, the leaching of phthalate is probably accentuated because of their lipophilic profile.

Acknowledgement

The authors acknowledge Maude Galonnier, Tiffany Masnou, Anna Legrand and Virginie Murez for their contribution to this work. They also wish to acknowledge Richard Roe for checking English language.

Appendix A. Supplementary data

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.fct.2019.03.030>.

References

O'Neil, M.J., Merck & Co (Eds.), 2006. *The Merck Index: an Encyclopedia of Chemicals,*

- Drugs, and Biologicals, 14. Merck handbooks. Merck, Whitehouse Station, NJ.
- AFNOR, 2011. ISO 12787: Cosmetics - Analytical Methods - Validation Criteria for Analytical Results Using Chromatographic Techniques (No. ISO 12787).
- AFNOR, 2014. Cosmétiques — Méthodes analytiques — Méthode CG-SM pour l'identification et l'analyse de 12 phthalates dans des échantillons de produits cosmétiques prêts à être injectés dans un système analytique. 71.100.70.
- Agence nationale de sécurité sanitaire alimentation, environnement, travail, 2015. *Connaissances relatives à la réglementation, à l'identification, aux propriétés chimiques, à la production et aux usages des composés de la famille des phthalates (Tome 1) (Rapport d'étude)*. Maison-Alfort.
- Amiridou, D., Voutsas, D., 2011. Alkylphenols and phthalates in bottled waters. *J. Hazard Mater.* 185, 281–286. <https://doi.org/10.1016/j.jhazmat.2010.09.031>.
- Bach, C., Dauchy, X., Chagnon, M.-C., Etienne, S., 2012. Chemical compounds and toxicological assessments of drinking water stored in polyethylene terephthalate (PET) bottles: a source of controversy reviewed. *Water Res.* 46, 571–583. <https://doi.org/10.1016/j.watres.2011.11.062>.
- Bi, X., Pan, X., Yuan, S., Wang, Q., 2013. Plasticizer contamination in edible vegetable oil in a U.S. Retail market. *J. Agric. Food Chem.* 61, 9502–9509. <https://doi.org/10.1021/jf402576a>.
- Bignardi, C., Cavazza, A., Laganà, C., Salvadeo, P., Corradini, C., 2017. Release of non-intentionally added substances (NIAS) from food contact polycarbonate: effect of ageing. *Food Control* 71, 329–335. <https://doi.org/10.1016/j.foodcont.2016.07.013>.
- Bradley, Coulter, 2007. *An Investigation into the Reaction and Breakdown Products from Starting Substances Used to Produce Food Contact Plastics (No. FD 07/01)*. Food Standards Agency.
- Bureau for Chemical Substances, 2013. *Proposal for Identification of a Substance as a CMR CAT 1A or 1B, PBT, vPvB or a Substance of an Equivalent Level of Concern - Dipentyl Phthalate*.
- Cacho, J.I., Campillo, N., Viñas, P., Hernández-Córdoba, M., 2012. Determination of alkylphenols and phthalate esters in vegetables and migration studies from their packages by means of stir bar sorptive extraction coupled to gas chromatography–mass spectrometry. *J. Chromatogr. A* 1241, 21–27. <https://doi.org/10.1016/j.chroma.2012.04.018>.
- Cao, X.-L., 2008. Determination of phthalates and adipate in bottled water by headspace solid-phase microextraction and gas chromatography/mass spectrometry. *J. Chromatogr. A* 1178, 231–238. <https://doi.org/10.1016/j.chroma.2007.11.095>.
- Careghini, A., Mastorgio, A.F., Saponaro, S., Sezenna, E., 2015. Bisphenol A, nonylphenols, benzophenones, and benzotriazoles in soils, groundwater, surface water, sediments, and food: a review. *Environ. Sci. Pollut. Res.* 22, 5711–5741. <https://doi.org/10.1007/s11356-014-3974-5>.
- Casajuana, N., Lacorte, S., 2004. New methodology for the determination of phthalate esters, bisphenol a, bisphenol a diglycidyl ether, and nonylphenol in commercial whole milk samples. *J. Agric. Food Chem.* 52, 3702–3707. <https://doi.org/10.1021/jf040027s>.
- Charron, C., De Vaugelade, S., Richard, F., Largitte, A., Pirnay, S., 2018. Optimization of the method of the content-containing interaction evaluation for cosmetic products by gas chromatography–mass spectrometry. *Int. J. Cosmet. Sci.* 40, 269–275. <https://doi.org/10.1111/ics.12460>.
- Chen, H., Wang, C., Wang, X., Hao, N., Liu, J., 2005. Determination of phthalate esters in cosmetics by gas chromatography with flame ionization detection and mass spectrometric detection. *Int. J. Cosmet. Sci.* 27, 205–210.
- Cirillo, T., Latini, G., Castaldi, M.A., Dipaola, L., Fasano, E., Esposito, F., Scognamiglio, G., Francesco, F.D., Cobellis, L., 2015. Exposure to di-2-ethylhexyl phthalate, di-*N*-butyl phthalate and bisphenol a through infant formulas. *J. Agric. Food Chem.* 63, 3303–3310. <https://doi.org/10.1021/jf505563k>.
- Council of Europe, European Directorate for the Quality of Medicines & HealthCare (EDQM), 2010. *European Pharmacopoeia*. Council of Europe, Strasbourg.
- Environment Agency Austria, 2012. *Proposal for Identification of a Substance as a CMR CAT 1A or 1B, PBT, vPvB or a Substance of an Equivalent Level of Concern - Diisopentylphthalate*.
- European Chemicals Agency, 2009. *15 New Substances of Very High Concern to Be Added to the Candidate List [Press Release]*.
- European Chemicals Agency, 2010. *Evaluation of New Scientific Evidence Concerning the Restrictions Contained in Annex XVII to Regulation (EC) No 1907/2006 (REACH) - Review of New Available Information for Benzyl Butyl Phthalate*.
- European Commission, 2011. *Commission Regulation (EU) No 10/2011 of 14 January 2011 on Plastic Materials and Articles Intended to Come into Contact with Food (Regulation No. 10/2011)*. European Union.
- European Commission, 2018. *Commission Regulation (EU) 2018/213 of 12 February 2018 on the Use of Bisphenol A in Varnishes and Coatings Intended to Come into Contact with Food and Amending Regulation (EU) No 10/2011 as Regards the Use of that Substance in Plastic Food Contact Materials (Regulation No. 2018/213)*.
- European Directorate for the Quality of Medicines & HealthCare (EDQM), 2013. *3.1 Materials and containers*. In: *European Pharmacopoeia*. Council of Europe, Strasbourg.
- European Parliament and Council of the European Union, 2009. *Regulation (EC) No 1223/2009 of the European Parliament and of the Council of 30 November 2009 on Cosmetic Products (Regulation No. 1223/2009)*. European Union.
- European Parliament and Council of the European Union, 2017. *Regulation (EU) 2017/745 of the European Parliament and of the Council of 5 April 2017 on Medical Devices (Regulation No. 2017/745)*.
- Fabjan, E., Hulzebos, E., Mennes, W., Piersma, A.H., 2006. A category Approach for reproductive effects of phthalates. *Crit. Rev. Toxicol.* 36, 695–726. <https://doi.org/10.1080/10408440600894914>.
- Fasano, E., Bono-Blay, F., Cirillo, T., Montuori, P., Lacorte, S., 2012. Migration of phthalates, alkylphenols, bisphenol A and di(2-ethylhexyl)adipate from food

- packaging. *Food Control* 27, 132–138. <https://doi.org/10.1016/j.foodcont.2012.03.005>.
- Federal Institute for Occupational Safety and Health, 2011. Proposal for Identification of a Substance as a CMR CAT 1A or 1B, PBT, vPvB or a Substance of an Equivalent Level of Concern - Bis(2-Methoxyethyl) Phthalate.
- Federal Institute for Occupational Safety and Health, 2012. Proposal for Identification of a Substance as a CMR CAT 1A or 1B, PBT, vPvB or a Substance of an Equivalent Level of Concern - N-Pentyl-Isopentyl Phthalate.
- Federal Institute for Occupational Safety and Health, 2013. Proposal for Identification of a Substance as a CMR CAT 1A or 1B, PBT, vPvB or a Substance of an Equivalent Level of Concern - Dihexyl Phthalate.
- Feng, C.-H., Jiang, S.-R., 2012. Micro-scale quantitation of ten phthalate esters in water samples and cosmetics using capillary liquid chromatography coupled to UV detection: effective strategies to reduce the production of organic waste. *Microchim. Acta* 177, 167–175. <https://doi.org/10.1007/s00604-012-0761-1>.
- Ferrer, E., Santoni, E., Vittori, S., Font, G., Mañes, J., Sagratini, G., 2011. Simultaneous determination of bisphenol A, octylphenol, and nonylphenol by pressurised liquid extraction and liquid chromatography-tandem mass spectrometry in powdered milk and infant formulas. *Food Chem.* 126, 360–367. <https://doi.org/10.1016/j.foodchem.2010.10.098>.
- Fierens, T., Servaes, K., Van Holderbeke, M., Geerts, L., De Henauw, S., Sioen, I., Vanermen, G., 2012. Analysis of phthalates in food products and packaging materials sold on the Belgian market. *Food Chem. Toxicol.* 50, 2575–2583. <https://doi.org/10.1016/j.fct.2012.04.029>.
- García Ibarra, V., Rodríguez Bernaldo de Quirós, A., Paseiro Losada, P., Sendón, R., 2018. Identification of intentionally and non-intentionally added substances in plastic packaging materials and their migration into food products. *Anal. Bioanal. Chem.* 410, 3789–3803. <https://doi.org/10.1007/s00216-018-1058-y>.
- Gimeno, P., Maggio, A.-F., Bousquet, C., Quioirez, A., Cívade, C., Bonnet, P.-A., 2012. Analytical method for the identification and assay of 12 phthalates in cosmetic products: application of the ISO 12787 international standard “Cosmetics-Analytical methods-Validation criteria for analytical results using chromatographic techniques. *J. Chromatogr. A* 1253, 144–153. <https://doi.org/10.1016/j.chroma.2012.06.090>.
- Gimeno, P., Thomas, S., Bousquet, C., Maggio, A.-F., Cívade, C., Brenier, C., Bonnet, P.-A., 2014. Identification and quantification of 14 phthalates and 5 non-phthalate plasticizers in PVC medical devices by GC-MS. *J. Chromatogr. B* 949–950, 99–108. <https://doi.org/10.1016/j.jchromb.2013.12.037>.
- Gomez-Berrada, M.P., Ficheux, A.S., Galonnier, M., Rolfo, J.E., Rielland, A., Guillou, S., De Javel, D., Roudot, A.C., Ferret, P.J., 2017. Influence of the container on the consumption of cosmetic products. *Food Chem. Toxicol.* 109, 230–236. <https://doi.org/10.1016/j.fct.2017.09.005>.
- Guo, Y., Kannan, K., 2013. A survey of phthalates and parabens in personal care products from the United States and its implications for human exposure. *Environ. Sci. Technol.* 47, 14442–14449. <https://doi.org/10.1021/es4042034>.
- Guo, Y., Zhang, Z., Liu, L., Li, Y., Ren, N., Kannan, K., 2012. Occurrence and profiles of phthalates in foodstuffs from China and their implications for human exposure. *J. Agric. Food Chem.* 60, 6913–6919. <https://doi.org/10.1021/jf3021128>.
- Hahladakis, J.N., Velis, C.A., Weber, R., Iacovidou, E., Purnell, P., 2018. An overview of chemical additives present in plastics: migration, release, fate and environmental impact during their use, disposal and recycling. *J. Hazard Mater.* 344, 179–199. <https://doi.org/10.1016/j.jhazmat.2017.10.014>.
- Haynes, W.M., 2014. *CRC Handbook of Chemistry and Physics, 95th Edition*. CRC Press, Hoboken.
- Howard, P.H., Chemical Rubber Company (Eds.), 1997. *Handbook of Physical Properties of Organic Chemicals*. Lewis Publ, Boca Raton.
- Jeilani, Y.A., Cardelino, B.H., Ibeanusi, V.M., 2011. Density functional theory and mass spectrometry of phthalate fragmentations mechanisms: modeling hyperconjugated carbocation and radical cation complexes with neutral molecules. *J. Am. Soc. Mass Spectrom.* 22, 1999–2010. <https://doi.org/10.1007/s13361-011-0215-8>.
- Jenke, D.R., Jene, J.M., Poss, M., Story, J., Tsilipetros, T., Odufu, A., Terbush, W., 2005. Accumulation of extractables in buffer solutions from a polyolefin plastic container. *Int. J. Pharm.* 297, 120–133. <https://doi.org/10.1016/j.ijpharm.2005.03.010>.
- Jenke, D., Castner, J., Egert, T., Feinberg, T., Hendrickner, A., Houston, C., Hunt, D.G., Lynch, M., Shaw, A., Nicholas, K., Norwood, D.L., Paskiet, D., Ruberto, M., Smith, E.J., Holcomb, F., 2013. Extractables characterization for five materials of construction representative of packaging systems used for parenteral and ophthalmic drug products. *PDA J. Pharm. Sci. Technol.* 67, 448–511. <https://doi.org/10.5731/pdajpst.2013.00933>.
- Larrañaga, M.D., Lewis, R.A., Lewis, R.J., Hawley, G.G., 2016. *Hawley's Condensed Chemical Dictionary*, sixteenth ed. John Wiley & Sons, Inc, Hoboken, New Jersey.
- Lateef, S.S., 2016. Extractables and Leachables Detected in Ophthalmic Drug Products - Detection and Identification Using High-Resolution LC/MS/MS.
- Lau, O.-W., Wong, S.-K., 2000. Contamination in food from packaging material. *J. Chromatogr. A* 882, 255–270.
- Meeker, J.D., Sathyanarayana, S., Swan, S.H., 2009. Phthalates and other additives in plastics: human exposure and associated health outcomes. *Philos. Trans. R. Soc. B Biol. Sci.* 364, 2097–2113. <https://doi.org/10.1098/rstb.2008.0268>.
- Muncke, J., 2011. Endocrine disrupting chemicals and other substances of concern in food contact materials: an updated review of exposure, effect and risk assessment. *J. Steroid Biochem. Mol. Biol.* 127, 118–127. <https://doi.org/10.1016/j.jsbmb.2010.10.004>.
- Nerin, C., Alfaro, P., Aznar, M., Domeño, C., 2013. The challenge of identifying non-intentionally added substances from food packaging materials: a review. *Anal. Chim. Acta* 775, 14–24. <https://doi.org/10.1016/j.aca.2013.02.028>.
- Net, S., Sempéré, R., Delmont, A., Paluselli, A., Ouddane, B., 2015. Occurrence, fate, behavior and ecotoxicological state of phthalates in different environmental matrices. *Environ. Sci. Technol.* 49, 4019–4035. <https://doi.org/10.1021/es505233b>.
- Pan, C., Harmon, F., Toscano, K., Liu, F., Vivilecchia, R., 2008. Strategy for identification of leachables in packaged pharmaceutical liquid formulations. *J. Pharm. Biomed. Anal.* 46, 520–527. <https://doi.org/10.1016/j.jpba.2007.11.032>.
- Roberts, D., Feilden, A., Barlow, R., D'Silva, K., Silcock, P., 2016. Confident identification of leachable impurities from pharmaceutical container closure materials using orbitrap-mass-spectrometer-based GC-MS. (application note).
- Scientific Committee on Consumer Safety, 2015. *The SCCS Notes of Guidance for the Testing of Cosmetic Ingredients and Their Safety Evaluation 9th Revision (Guidance No. SCCS/1564/15)*. European Commission.
- Sekizawa, J., Dobson, S., Touch, R.J., 2003. *Diethyl Phthalate, Concise International Chemical Assessment Document*. World Health Organization, Geneva.
- Shen, H.-Y., Jiang, H.-L., Mao, H.-L., Pan, G., Zhou, L., Cao, Y.-F., 2007. Simultaneous determination of seven phthalates and four parabens in cosmetic products using HPLC-DAD and GC-MS methods. *J. Sep. Sci.* 30, 48–54. <https://doi.org/10.1002/jssc.200600215>.
- Thomas, C., Siong, D., Pirnay, S., 2014. Evaluation of the content - containing interaction in cosmetic products using gas chromatography-mass spectrometry. *Int. J. Cosmet. Sci.* 36, 327–335. <https://doi.org/10.1111/ics.12130>.
- Thompson, R.C., Moore, C.J., vom Saal, F.S., Swan, S.H., 2009. Plastics, the environment and human health: current consensus and future trends. *Philos. Trans. R. Soc. B Biol. Sci.* 364, 2153–2166. <https://doi.org/10.1098/rstb.2009.0053>.
- Viñas, P., Campillo, N., Pastor-Belda, M., Oller, A., Hernández-Córdoba, M., 2015. Determination of phthalate esters in cleaning and personal care products by dispersive liquid-liquid microextraction and liquid chromatography-tandem mass spectrometry. *J. Chromatogr. A* 1376, 18–25. <https://doi.org/10.1016/j.chroma.2014.12.012>.
- Zhang, Y., Sun, S., Xing, X., Du, Z., Guo, Q., Yu, W., 2016. Detection and identification of leachables in vaccine from plastic packaging materials using UPLC-QTOF MS with self-built polymer additives library. *Anal. Chem.* 88, 6749–6757. <https://doi.org/10.1021/acs.analchem.6b01027>.