



HAL
open science

Nitrogen-Doped Carbon Dots/TiO₂ Nanoparticle Composites for Photoelectrochemical Water Oxidation

Hui Luo, Stoichko Dimitrov, Matyas Daboczi, Ji-Seon Kim, Qian Guo, Yuanxing Fang, Marc Antoine Stoeckel, Paolo Samori, Oliver Fenwick, Ana Belen Jorge Sobrido, et al.

► **To cite this version:**

Hui Luo, Stoichko Dimitrov, Matyas Daboczi, Ji-Seon Kim, Qian Guo, et al.. Nitrogen-Doped Carbon Dots/TiO₂ Nanoparticle Composites for Photoelectrochemical Water Oxidation. ACS Applied Nano Materials, 2020, 3 (4), pp.3371-3381. 10.1021/acsanm.9b02412 . hal-02898851

HAL Id: hal-02898851

<https://hal.science/hal-02898851v1>

Submitted on 13 Jul 2020

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Nitrogen-doped Carbon Dots/TiO₂ Nanoparticle Composites for Photoelectrochemical Water Oxidation

*Hui Luo,^{a,g} Stoichko Dimitrov,^{b,c} Matyas Daboczi,^d Ji-Seon Kim,^d Qian Guo,^a Yuanxing Fang,^e
Marc-Antoine Stoeckel,^f Paolo Samorì,^f Oliver Fenwick,^a Ana Belen Jorge Sobrido,^a Xinchun
Wang^e and Maria-Magdalena Titirici^{a,g}**

- a. School of Engineering and Materials Science, Queen Mary University of London, Mile End Road, E1 4NS, London, UK
- b. SPECIFIC, College of Engineering, Swansea University SA2 7AX, Swansea, UK
- c. School of Biological and Chemical Sciences, Queen Mary University of London, Mile End Road, E1 4NS, London, UK
- d. Department of Physics and Centre for Plastic Electronics, Imperial College London, South Kensington Campus, SW7 2AZ, London, UK
- e. State Key Laboratory of Photocatalysis on Energy and Environment, College of Chemistry, Fuzhou University, Fuzhou, 350116 P. R. China

1
2
3 f. Université de Strasbourg, CNRS, ISIS, 8, allée Gaspard Monge, 67000, Strasbourg,
4
5 France

6
7
8
9 g. Department of Chemical Engineering, Imperial College London, South Kensington
10
11 Campus, SW7 2AZ, London, UK

12
13
14 Corresponding author e-mail: m.titirici@imperial.ac.uk

15
16
17 **KEYWORDS:** Carbon dots, Photoelectrocatalysis, Heterojunction, Charge transfer, Band
18
19 structure

20
21
22
23 **ABSTRACT**

24
25
26
27 Carbon dots on photoactive semiconductor nanomaterials have represented an effective strategy
28
29 for enhancing their photoelectrochemical (PEC) activity. By carefully designing and manipulating
30
31 carbon dots/support composite, a high photocurrent could be obtained. Currently, there is not much
32
33 fundamental understanding of how the interaction between such materials can facilitate the
34
35 reaction process. This hinders the wide applicability in PEC devices. To address this need of
36
37 improving the fundamental understanding of carbon dots/semiconductor nanocomposite, we have
38
39 taken the TiO₂ case as a model semiconductor system with nitrogen-doped carbon dots (NCDs).
40
41 We present here with in-depth investigation of the structural hybridization and energy transitions
42
43 in the NCDs/TiO₂ photoelectrode *via* high-resolution scanning transmission microscopy (HR-
44
45 STEM), electron energy loss spectroscopy (EELS), UV-Vis absorption, electrochemical
46
47 impedance spectroscopy (EIS), Mott-Schottky (M-S), time-correlated single photon counting
48
49 (TCSPC) and ultra-violet photoelectron spectroscopy (UPS), which shed some light on the charge
50
51 transfer process at the carbon dots and TiO₂ interface. We show that N doping in carbon dots can
52
53
54
55
56
57
58
59
60

effectively prolong the carrier lifetime, and the hybridisation of NCDs and TiO₂ is able not only to extend TiO₂ light response into the visible range but also to form heterojunction at the NCDs/TiO₂ interface with properly aligned band structure that allows a spatial separation of the charges. This work is arguably the first to report the direct probing of the band positions of carbon dots-TiO₂ nanoparticle composite in a PEC system for understanding the energy transfer mechanism, demonstrating the favourable role of NCDs in the photocurrent response of TiO₂ for water oxidation process. This study reveals the importance of combining structural, photophysical and electrochemical experiments to develop a comprehensive understanding of the nanoscale charge transfer processes between the carbon dots and their catalyst supports.

1. Introduction

Photoelectrochemical (PEC) water splitting for hydrogen and oxygen production represents a promising technology for the conversion of solar energy to clean and renewable chemical fuels. Since the first report on PEC water splitting in 1972 using TiO₂ photoelectrode,¹ many efforts have been made to improving the light conversion efficiency. To achieve the overall reaction, the water oxidation happening at photoanode is a crucial step as it requires higher energy input. Several approaches have been reported in the literature to improve the performance of the photoanode materials, such as heteroatom doping,² nanostructuring³ *etc.* Among those, constructing heterojunctions in nanoscale materials like CdS/TiO₂,⁴⁻⁸ graphene/TiO₂,^{9,10} carbon dots/TiO₂¹¹⁻¹⁵ has been demonstrated to be an effective strategy. The enhanced PEC performance of the CdS/TiO₂ system is assigned to the electric-field-assisted charge transport at the interface with matched band alignments, which can improve the charge separation and prolong the photo-induced carrier lifetime. In the case of graphene or reduced graphene oxide, those 2D and zero bandgap


1
2
3 materials serve as electron mediator when coupled with TiO₂, allowing an accelerated electron
4 migration at the interface.
5
6

7
8 Carbon dots with size less than 10 nm have been demonstrated to act as photosensitizers for
9 enhancing the performance of heterogeneous photocatalysts, due to their adjustable band
10 potentials, excellent and tunable light-harvesting ability, and electron transfer efficiency.^{12,16–20}
11
12 When doped with nitrogen,^{13,21,22} carbon dots usually show an enhanced activity towards photo-
13 driven reactions both experimentally and theoretically.^{23,24} Accordingly, the utilisation of nitrogen-
14 doped carbon dots (NCDs) photosensitizers to facilitate PEC reactions started to attract
15 attention.^{13,21,25} However, owing to the complexity of NCDs compare to CdS and graphene in
16 terms of chemical structure and energy states, the mechanism of NCDs in improving the PEC
17 performance is still not well understood and explained.^{12,17,26} Previous studies have indirectly
18 demonstrated that the electronic coupling between the π states of the CDs and the conduction band
19 of TiO₂ can form heterojunctions and impart the system for visible light absorption. The resulting
20 heterojunction can efficiently separate the photo-generated electrons and holes, resulting in a lower
21 recombination rate and a higher PEC activity.¹⁴ Those effects can be greatly influenced by the
22 intrinsic properties of CDs. For instance, the graphitisation degree can affect the charge transfer
23 process,²⁷ the different N doping configuration (amines, amides, pyridinic, quaternary, N-oxides,
24 etc.) can govern the light-harvesting ability,²⁸ while the functionality would determine the
25 interaction with supporting materials.^{16,29} Hence, it is of vital importance to develop a deeper
26 understanding of the nanostructure of CDs and their interaction with the semiconductor materials
27 and gain further insights on the dynamics of the charge exchange process at the materials interface.
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

50
51 In this paper, we exploit a broad arsenal of complementary advanced characterisation technique
52 to understand the morphology, structure, optical and electrochemical properties of chitosan derived
53
54
55
56
57
58
59
60

NCDs at a fundamental level. Such studies reveal that N doping can effectively prolong the photo-induced carrier lifetime. A photoanode was prepared by decorating the as-synthesized NCDs onto a TiO₂ mesoporous film, which is used as a model semiconductor material to study the NCDs/semiconductor interaction. A detailed structural and PEC analysis showed that the nanoparticle composite possesses an improved visible light response as well as charge separation/transport ability, which resulted in a higher photocurrent value. In-depth characterisation of the NCD/TiO₂ nanocomposite by methods such as Mott-Schottky analysis, photoelectron spectroscopy in air, Kelvin probe and ultra-violet photoelectron spectroscopy was employed to evaluate the energy levels. Combined with electrochemical impedance spectroscopy (EIS) and in-situ photoluminescence quenching by time-correlated single photon counting (TCSPC), we present here the detailed mechanism for the interfacial charge transfer process.

2. Results and discussion

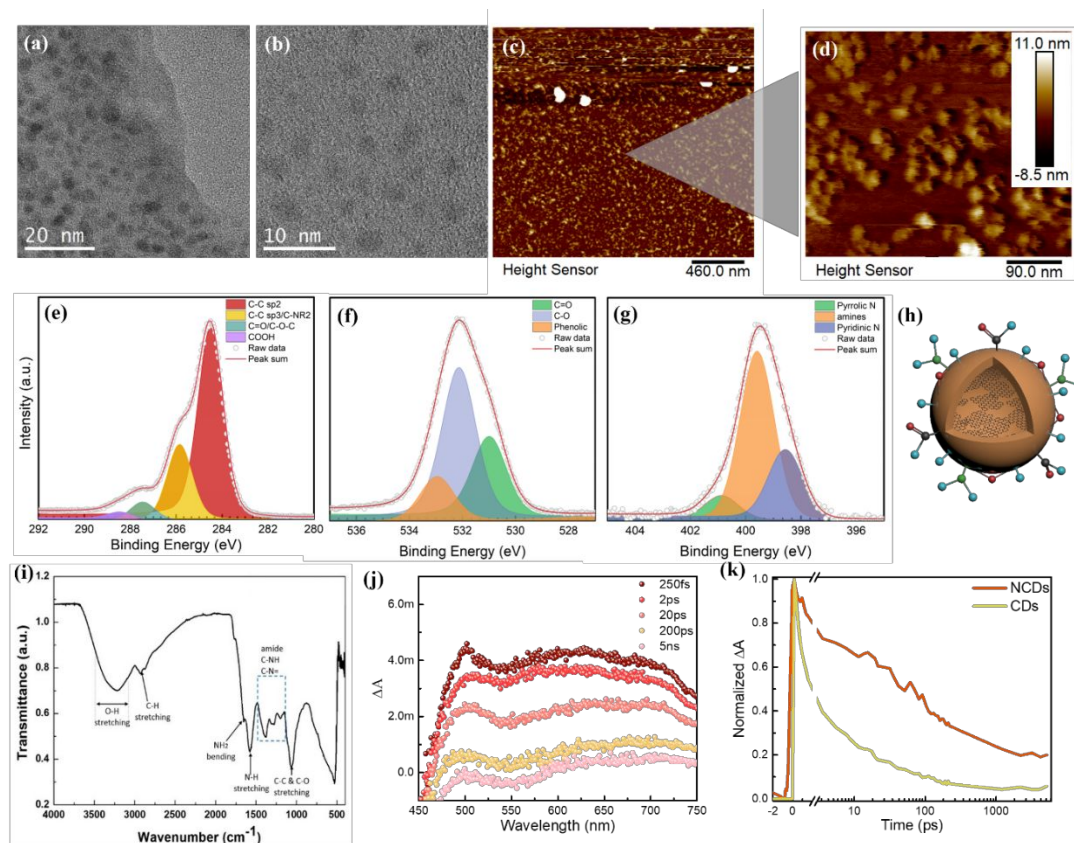

1
2
3 **Figure 1** Structural features of as-prepared NCDs: TEM (a) and HR-TEM (b) images; (c) an
4 overview AFM image on mica substrate (Z scale -6.0 to 7.9 nm) and (d) high-resolution scanned
5 image; XPS spectra: (e) C 1s, (f) O 1s, (g) N 1s and corresponding FTIR (i) spectrum; (h) a
6
7 schematic structure based on the characterizations (atoms in red: O, green: N and blue: H); (j) fs-
8
9 TAS spectra at different time decays and (k) normalized fs-TAS kinetics of NCDs and non-doped
10
11 CDs measured at 500 nm (excitation wavelength: 375 nm).

12
13
14
15
16
17 NCDs were synthesized by solvothermal carbonisation of chitosan in ethanol solvent (4% w/v).
18
19 Several works on using chitosan to produce NCDs have been reported earlier.³⁰⁻³² Under mild
20
21 conditions (HTC with 180 °C), the carbonisation and functionalisation will take place through
22
23 chitosan dehydration, leading to the formation of NCDs. As illustrated in **Figure S1**, the precursor
24
25 molecules go through decomposition to HMF and ammonia. The HMF molecule then go through
26
27 ring opening to react with ammonia and form aminopentanal. Intermolecular condensation would
28
29 occur at this stage in these intermediates. Pyridines would form from the reaction between amino
30
31 groups and aldehyde, while the reaction between amino and keto groups results in the formation
32
33 of pyrroles. Some amines remain free from reacting with other groups.³³ These functionalities are
34
35 later identified in the structure of NCDs.

36
37
38
39
40 **Figure 1(a, b)** shows the transmission electron microscopy (TEM) images of NCDs with
41
42 spherical morphologies. The atomic force microscopy (AFM) images of the NCDs (**Figure 1c, d**)
43
44 further prove that the sizes of those NCDs are uniformly distributed. The CDs are ~ 2-8 nm in
45
46 height, values obtained from cross-sectional topographic measurements, taken into account the
47
48 broadening effect due to the finite size of the tip.

49
50
51 To analyse the structure of the carbon core, the output of XRD and Raman spectroscopy
52
53 techniques were compared. The X-ray diffraction (XRD) pattern (**Figure S2a**) displays a broad
54
55

1
2
3 peak centred at 21° , which has been demonstrated to be amorphous with turbostratic structure in
4
5 our previous study.³¹ In theory, XRD involves X-rays interacting with electrons to reveal the
6
7 reciprocal space of crystalline lattice by diffraction, which does not give sufficient structural
8
9 information of packed carbon dots due to the less ordered structure. In this regard, Raman
10
11 spectroscopy uses long wavelength radiation and interacts with atoms, molecules or ions, which
12
13 can reveal the vibration frequencies of the system by scattering, providing information about the
14
15 chemical environments. Hence here Raman spectroscopy was carried out for the surface
16
17 characterisation of partially ordered carbon materials.³⁴ **Figure S2b** shows the Raman spectra (λ
18
19 = 633 nm) of the NCDs. Two peaks centred at 1382 cm^{-1} and 1574 cm^{-1} can be seen, representing
20
21 the characteristic D and G bands for carbon materials, respectively, indicating a semi-crystalline
22
23 structure of the NCDs. The spectra show a significant level of noise-to-signal ratio, due to the
24
25 highly fluorescent background removal.
26
27
28
29

30
31 The X-ray photoelectron spectroscopy (XPS) spectra are shown in **Figure 1(e, f, g)**. They reveal
32
33 that the amine groups from chitosan are maintained on the surface of NCDs, and the carbon,
34
35 oxygen, nitrogen contents have been calculated to be 75.8%, 28.2% and 5.8%, respectively. Three
36
37 types of nitrogen species can be found in the material, which are pyridinic N (26%), amine groups
38
39 (64%) and pyrrolic N (10%), existing both on the surface as functional groups and incorporated
40
41 inside the core structure. It has been reported that different N-motifs show different charge
42
43 transportation properties, which will be beneficial for the PEC properties.²⁸ The Fourier transform
44
45 infrared (FTIR) spectrum in **Figure 1(i)** also confirms the existence of amine groups in the NCDs,
46
47 with NH_2 bending at 1648 cm^{-1} and N-H stretching at 1576 cm^{-1} . The peaks between 1151 and
48
49 1484 cm^{-1} are assigned to C-NH and C-N= amide groups.^{35,36} A schematic profile representing the
50
51 structure of NCDs is shown in **Figure 1h**.
52
53
54
55
56
57
58
59
60

1
2
3 The optical properties of the NCDs are analyzed by UV-Vis absorption and photoluminescence.
4
5 As shown in **Figure S3a**, the UV-Vis absorption spectrum of NCD solution exhibits strong, broad
6 light absorption in the ultraviolet range, with an absorption peak at 270 nm, which tails off in the
7 visible region. The 270 nm absorption peak is due to the $\pi \rightarrow \pi^*$ transition, while the visible light
8 absorption comes from $n \rightarrow \pi^*$ transition.^{37,38} The visible light response of the synthesized NCDs
9 is advantageous for use as a photosensitizer.¹⁴ In **Figure S3b**, excitation-dependent emission was
10 observed in the blue-green light region depending on the excitation wavelength, indicating easy
11 access to the electronic states ($n - \pi^*$, $\pi - \pi^*$).³⁹ These interesting optical properties grant the
12 NCDs with potential applications in hybrid PEC design. Photoluminescence quantum yield (Φ) of
13 NCDs was calculated to be 8.7% referenced by quinine sulphate (QS).⁴⁰
14
15
16
17
18
19
20
21
22
23
24
25

26 Our previous work has shown that the NCDs derived from chitosan are capable of generating
27 photocurrents under visible light irradiation, akin to the electronic structure of n-type
28 semiconductor, and the excited states of carbon dots upon interaction with light govern the photo-
29 induced activity.³¹ To investigate the nature of stable surface paramagnetic defects, EPR
30 measurements were performed on NCD powder at room temperature in dark condition. In **Figure**
31 **S4**, the sharp isotropic EPR signals centred at $g_{\text{iso}}=2.0035$ is expected to come from the presence
32 of carbon centred radical species present on the NCD surface, which could act as active sites for
33 redox reactions.
34
35
36
37
38
39
40
41
42
43

44 The excited state photophysical properties of NCDs were investigated by mean of femtosecond
45 transient absorption spectroscopy (fs-TAS) which reveals that upon 375 nm photoexcitation,
46 NCDs gave rise to differential absorption signals that are spanning over the visible range from
47 450-750 nm on a ps timescale (**Figure 1j**). Features are centred near 500 nm and 625 nm, similar
48 to previously reported spectra of CDs.^{27,37} The features showed up at shorter and longer
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 wavelenghtes are possibly assigned to core and surface states of CDs, respectively. This behaviour
4
5 is akin to that observed for graphitic carbon dots.^{27,41} The decay lifetime kinetics at 500 nm were
6
7 fitted using a bi-exponential function into short (2.17 ps, 39%) and long (138.97 ps, 61%) lived
8
9 components. The extracted excitons lifetimes have been found being longer than any other
10
11 photosensitising materials reported to date.^{42,43} The comparison of the decay profile of NCDs with
12
13 that of non-doped CDs in **Figure 1k** reveals that doping with N has largely prolonged the exciton
14
15 lifetime, being beneficial for the PEC process. This might be a result of N doping reducing π -
16
17 connections between sp^2 domains, suppressing the interlayer non-radiative energy dissipation,²¹
18
19 and serve as electron donor to effectively scavenge holes to extend the lifetime of photogenerated
20
21 electrons.²⁷ Here we have demonstrated for the first time clear evidence and explanation of the
22
23 positive effect of N doping in carbon dots for the application as efficient photosensitizers. We have
24
25 applied the prepared NCDs to TiO_2 , which is an ideal model semiconductor to study the effect of
26
27 the NCDs in the recombination rate of the photogenerated charge carriers in a PEC system.
28
29 Compared to inorganic semiconducting quantum dots, carbon dots consist of mostly sp^2 carbon,
30
31 which helps the formation of a charge-transfer complex with TiO_2 and thus resulting in more
32
33 efficient absorption and charge separation.⁴⁴
34
35
36
37
38
39

40 The TiO_2 thin film is fabricated by spin-coating a commercially available mesoporous titania
41
42 paste onto fluorine-doped tin oxide (FTO) coated glass substrate. To gain insight into the
43
44 morphology of the TiO_2 film, we performed SEM top-view and cross-section imaging of the
45
46 NCDs/ TiO_2 film, with representative images portrayed in **Figure S5**. No major aggregation of the
47
48 nanoparticles can be observed. The thickness of the film was measured to be $\sim 1 \mu m$ (from the
49
50 SEM cross-section), considered adequate to provide good charge carrier generation and collection
51
52 ability.⁴⁵ Brunauer-Emmett-Teller (BET) measurements showed that the TiO_2 has a specific
53
54
55
56
57
58
59
60

1
2
3 surface area of 110 m²/g, higher than the commercial P25 (49 m²/g). The mesoporosity, as seen
4
5 from the SEM top view image guarantees sufficient light absorption and is also beneficial for
6
7 anchoring the NCDs on its surface and inside the TiO₂ films, providing more active sites for
8
9 reactions.¹⁴
10

11
12 **Figure S6** displays the XRD patterns of the TiO₂ and NCDs/TiO₂ films. The dominant peak in
13
14 both samples are assigned to the (101) facet of anatase phase, which is considered to be the most
15
16 stable structure in anatase TiO₂.⁴⁶ The diffraction patterns of NCDs/TiO₂ are in good match with
17
18 that of the TiO₂ which contains mostly anatase phase with small amount of rutile (JCPDS 01-084-
19
20 1286, 01-073-2224), indicating that the deposition of NCDs does not cause any obvious changes
21
22 in TiO₂ crystallinity.⁴⁷
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

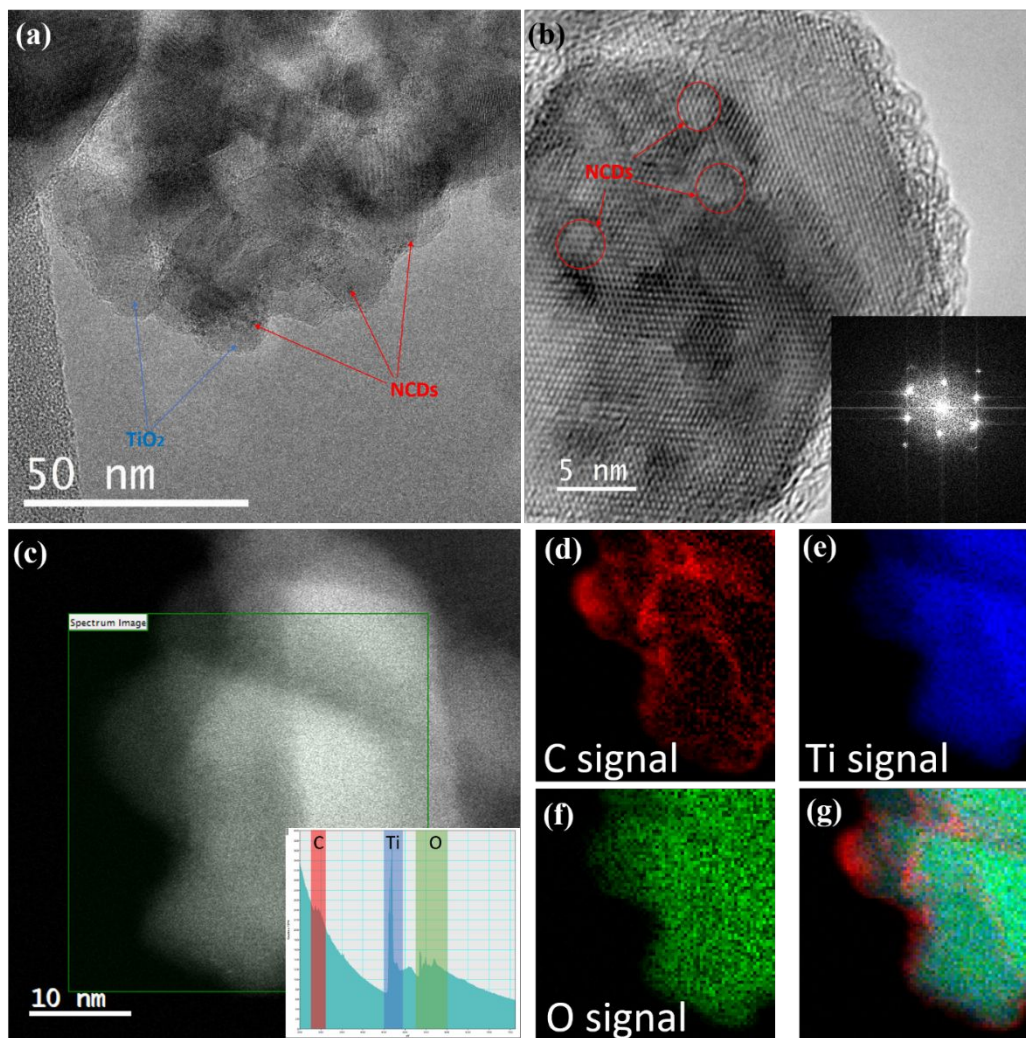


Figure 2 TEM (a) and HR-TEM (b) of NCDs/TiO₂ (insert is the FFT patterns); (c) HAADF image of NCDs/TiO₂ and corresponding EELS spectra (inserted). The single element maps derived from the spectra: (d) C signal, (e) Ti signal, (f) O signal and (g) colour mix (red: C, blue: Ti, green: O).

TEM and HR-TEM were used to investigate the morphologies of the NCDs/TiO₂ nanoparticles further. TEM image (**Figure 2a**) of the prepared NCDs/TiO₂ nanoparticles taken at low-magnification shows some dark spots dispersed on the surface of the TiO₂, revealing that the NCDs have been effectively deposited onto TiO₂. In the HR-TEM images, the NCDs became less obvious, leaving only contrast differences due to the small particle size and less crystalline nature

1
2
3 of the NCDs compared to TiO₂ nanoparticles, as determined by TEM and XRD (**Figure 1 and**
4 **S2**). The observed lattice spacing of 0.35 nm for TiO₂ nanoparticles correspond to the (101) plane
5 of anatase TiO₂, as can be seen from XRD patterns in **Figure S6**. To further resolve the presence
6 of NCDs, high-angle annular dark-field image (HAADF) was taken on several TiO₂ nanoparticles
7 under high magnification. As seen in **Figure 2c**, NCDs are difficult to discern through the dark-
8 field image due to the light element contrast. At the same area electron energy loss spectra (EELS)
9 was scanned. It is known that EELS is better than EDS at detecting light elements due to the
10 smaller energy window. Here we chose to look at 250 - 750 eV, which contains the characteristic
11 spectra of carbon, nitrogen, titanium and oxygen, as illustrated in **Figure 2c** inserted. The spectra
12 of C, Ti and O are very distinctive, while no signal can be seen from N, probably due to the low
13 nitrogen amount in the NCDs (N 5.8%) also loaded in small amounts on the TiO₂ (~2.4%
14 calculated from the mass loss in **Figure S7**). The EELS maps of individual elements along with
15 the colour mix are shown in **Figure 2(d-g)**. The mapping of the NCDs on TiO₂ infers the
16 heterostructure formation, which may promote the charge separation within the hybrid system,
17 corroborating the improved PEC activity.⁴⁸
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

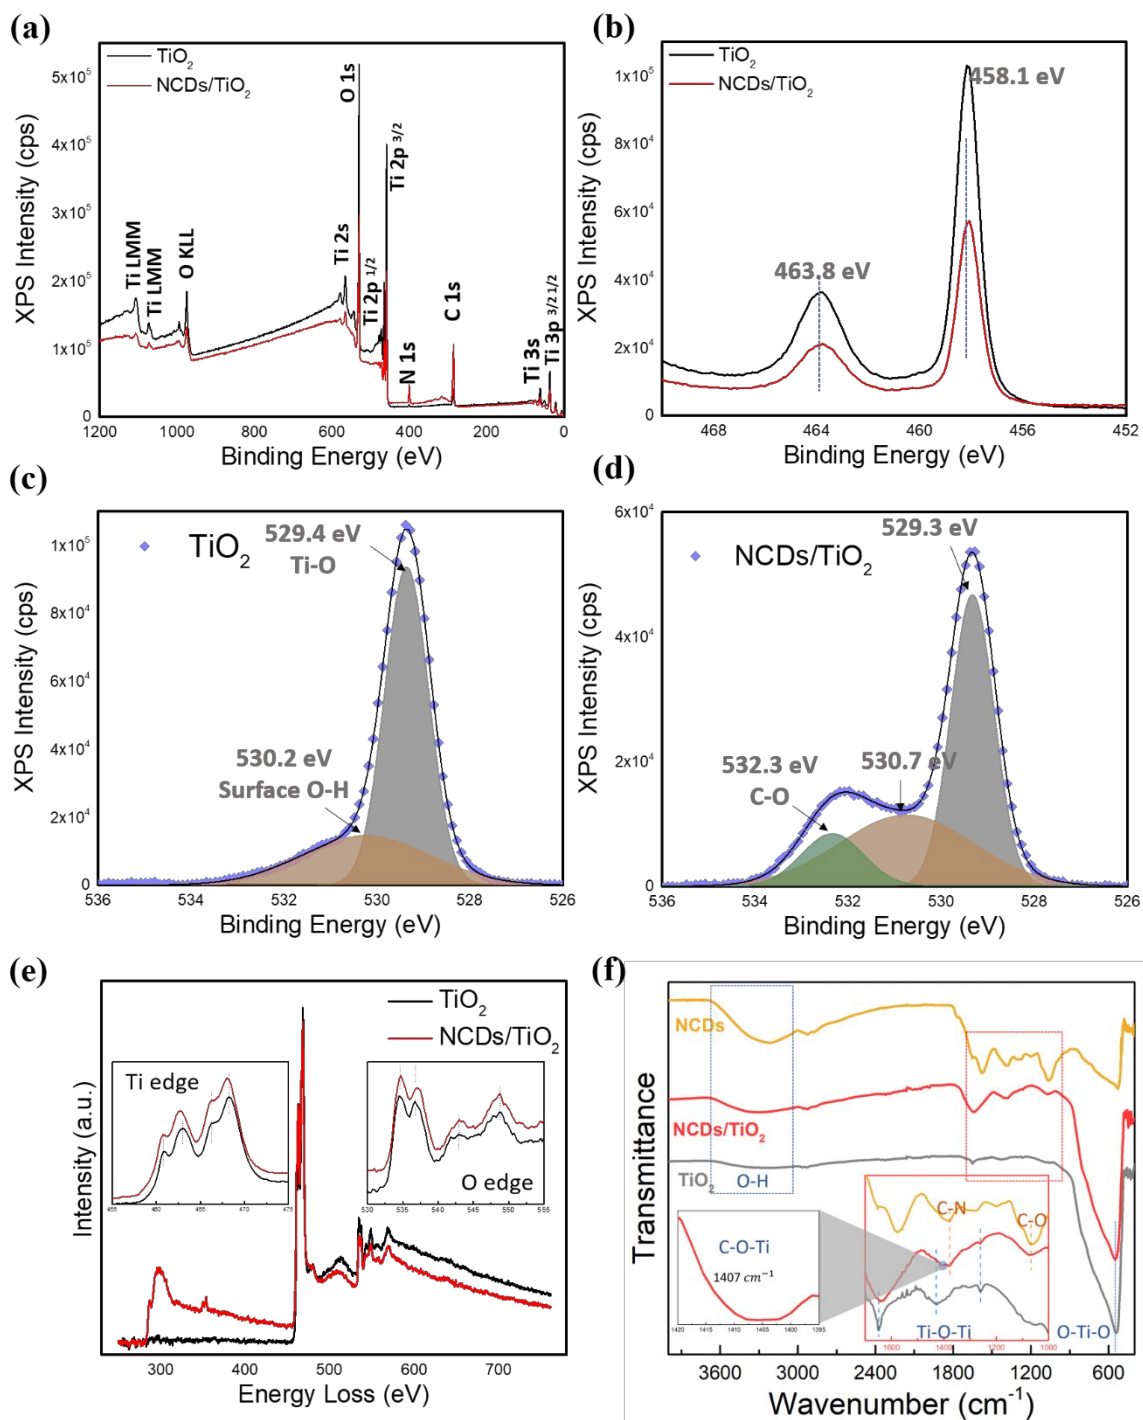


Figure 3 Comparison of XPS survey spectra (a) and Ti 2p high-resolution spectra (b) of the TiO₂ and NCDs/TiO₂ films; O 1s spectra of (c) TiO₂ and (d) NCDs/TiO₂. (e) EELS spectra of TiO₂ (black) and NCDs/TiO₂ (red) and (f) FTIR signals.

1
2
3 The chemical structure of the NCDs/TiO₂ was analysed by XPS. Compared to the pristine TiO₂,
4 the survey spectrum (**Figure 3a**) of NCDs/TiO₂ showed higher intensity in C and N peaks, which
5 originates from the NCDs. The deconvoluted high-resolution signals of Ti 2p (**Figure 3b**) show
6 no shift in the binding energy, suggesting that there is no disruption of the TiO₂ structure after
7 anchoring of the NCDs. The peaks at 458.1 eV and 463.8 eV are originated from the pair of Ti 2p_{3/2}
8 and Ti 2p_{1/2}, respectively, assigned to the Ti⁴⁺ sp peaks of TiO₂. **Figure 3c** shows the O 1s spectra
9 of TiO₂, in which the peaks at 529.4 eV and 530.2 eV arise from Ti-O and surface O-H groups in
10 TiO₂, respectively.⁴⁹ After depositing of NCDs, the surface O-H peak shifted towards higher
11 binding energy, suggesting that the chemical environment has been changed due to the interaction
12 between the TiO₂ and NCDs and the formation of the Ti-O-C bond.¹¹ The O 1s spectrum also
13 showed a peak at 532.3 eV corresponding to C-O bonds, which is also present in the O 1s spectra
14 of NCDs (**Figure 1f**). The energy shift can also be observed in high-resolution EELS spectra at Ti
15 and O edges after depositing NCDs (**Figure 3e**), suggesting a chemical environment change
16 around surface Ti and O atoms.^{50,51}

17
18
19 The formation of NCDs/TiO₂ hybrid has been further confirmed by FTIR analysis. **Figure 3f**
20 shows that the spectra of NCDs/TiO₂ display typical vibration of O-Ti-O at 550 cm⁻¹, as well as
21 C-N, C-O stretching at 1378 and 1067 cm⁻¹, confirming the presence of NCDs in the hybrid
22 sample. A new absorption peak arises between the Ti-O-Ti and C-N bond at 1407 cm⁻¹, which is
23 possible through the C-O-Ti bond formation.⁵² Based on the above results, it can be concluded that
24 the NCDs are loaded on the TiO₂ *via* chemical absorption.
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

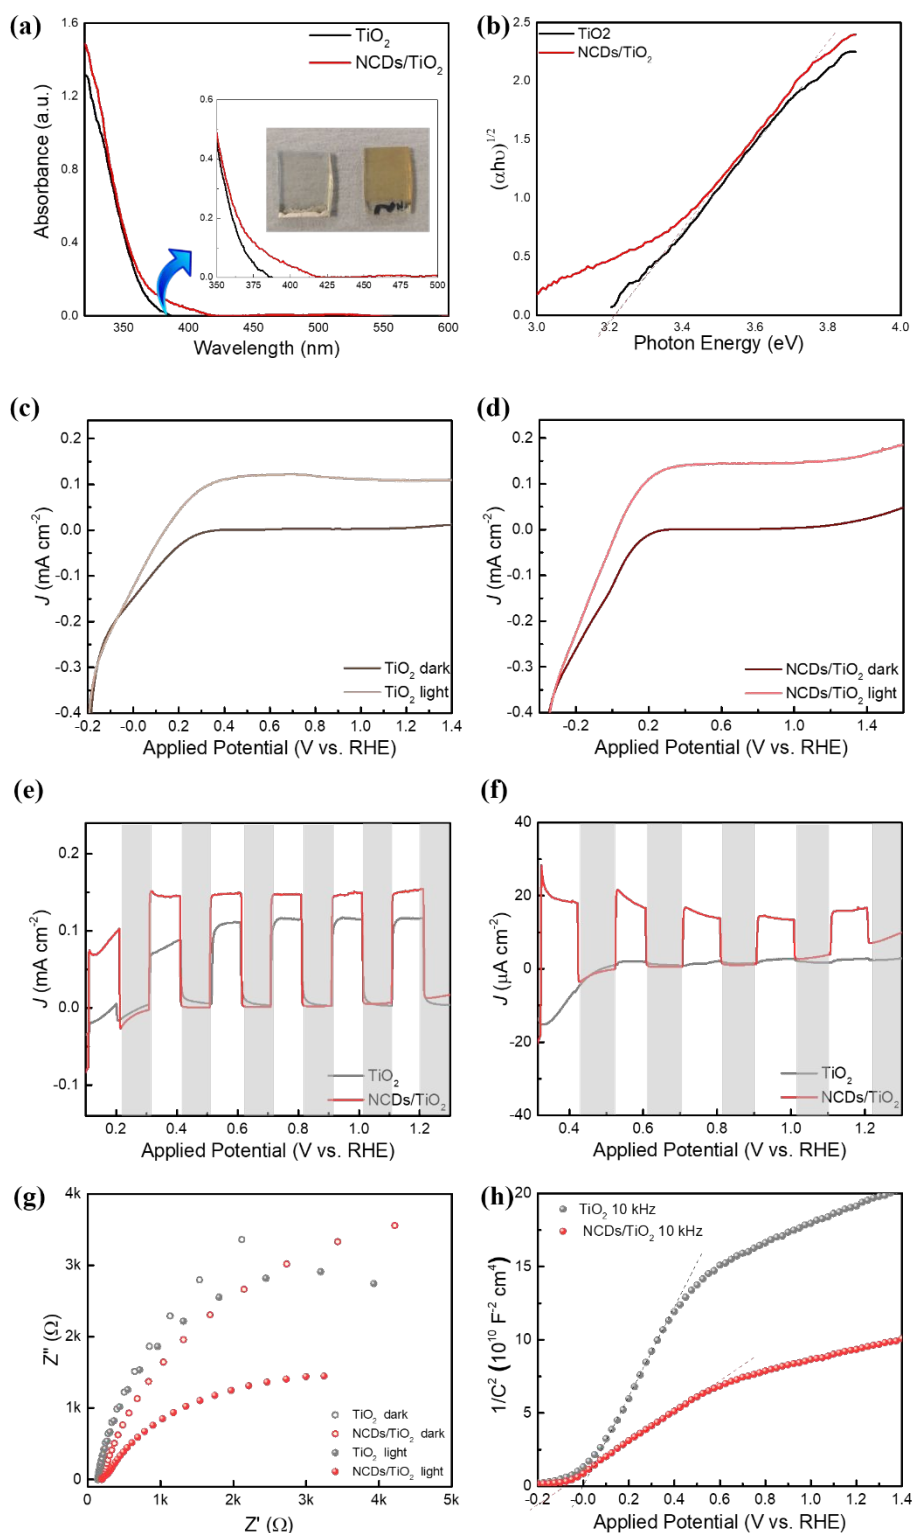


Figure 4 optoelectronic properties of TiO_2 and NCDs/TiO_2 films: (a) UV-Vis absorption (inserted are the digital pictures of the films: left: TiO_2 , right: NCDs/TiO_2); (b) tauc plot of TiO_2 and

1
2
3 NCDs/TiO₂ with indirect band gap; LSV curves of (c) TiO₂ and (d) NCDs/TiO₂ under dark and
4 light conditions; the chopped photocurrent response of the two samples under (e) full spectrum
5 and (f) visible light ($\lambda > 420$ nm) illumination; (g) EIS Nyquist plots under simulated solar light
6 illumination (100 kHz – 0.1 Hz, 0.3V vs. RHE, 100 mW cm⁻²) and (h) Mott-Schottky plots with
7 10 kHz frequency under dark condition at equilibrium.
8
9
10
11
12
13
14

15 Light absorption is one of the essential factors determining the PEC performance of electrode
16 materials. UV-Vis-NIR spectroscopy is employed to characterise the optical properties of the TiO₂
17 films and their respective NCD hybrids. As shown in **Figure 4a**, pure TiO₂ show no absorption
18 above 385 nm owing to the intrinsic wide band gap of anatase TiO₂ (3.2 eV). Compared to the
19 pristine TiO₂ film, the NCD decorated films show enhanced visible light absorption tails up to 425
20 nm for NCDs/TiO₂. Therefore, the presence of NCDs plays a critical role in boosting the visible
21 light absorption of the composites, which is important for visible-light-driven
22 photoelectrocatalytic activity. No bandgap narrowing can be observed from the Tauc plot (**Figure**
23 **4b**), indicating that the NCDs are only present on the surface without disrupting the crystalline
24 structure of TiO₂, in line with the STEM and XRD results.
25
26
27
28
29
30
31
32
33
34
35
36
37

38 PEC measurements were performed on the aforementioned TiO₂ films to investigate the photo-
39 induced charge transfer behaviour. **Figure 4c-f** show the linear sweep voltammetry (LSV) of the
40 photoelectrodes under simulated solar light irradiation (electrolyte: 0.2 M Na₂SO₄ aqueous
41 solution; scan rate: 5 mV/s). Clearly, the NCDs/TiO₂ photoanode showed enhanced photo-
42 response compared to pure TiO₂; the NCDs/TiO₂ displays a saturation photocurrent of 0.15 mA
43 cm⁻² at 0.3V vs RHE, approximately two times higher than that of the pristine TiO₂ (0.08 mA cm⁻²)
44 under the same conditions. This may be the effect of the formation of heterojunctions at the
45 NCDs/TiO₂ interface, which can effectively separate the photo-induced charge carriers. The
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 expected PEC results under visible light ($\lambda > 420$ nm) further depict the enhanced charge
4 separation of TiO_2 by hybridising NCDs. While TiO_2 electrode showed no obvious photo-response
5
6 in this region, the NCDs/ TiO_2 generated photocurrent of $17 \mu\text{A cm}^{-2}$, owing to the slightly
7
8 enhanced visible absorption of NCDs. Consequently, based on the above results, the
9
10 photosensitization effect of NCDs on the photocurrent generation of NCDs/ TiO_2 heterostructures
11
12 was unambiguously ascertained under both simulated solar and visible light illuminations.
13
14
15

16
17 The distribution of the photocurrent between UV and visible light is given in **Figure S8**. Nearly
18
19 half of the enhanced photo-carrier generation of NCDs/ TiO_2 is attributed to the higher visible light
20
21 absorption, due to the photosensitization ability of NCDs. The rest of the improved photocurrent
22
23 may arise from a more efficient charge separation and transportation because of the formed
24
25 heterojunction between TiO_2 and NCDs.^{29,53} Stability test was performed on the NCDs/ TiO_2
26
27 photoelectrode. As seen from **Figure S9**, NCDs/ TiO_2 exhibit a current density decrease in the first
28
29 2000s, but with time proceeds, the electrode became more stable, with less than 25 % current
30
31 density drop. Future work is needed to improve the stability of this hybridized material.
32
33
34

35
36 The electron-hole pair separation efficiency were further analysed with EIS measurements. In
37
38 the Nyquist plots, the charge transfer process at the electrode/electrolyte interface is represented
39
40 by the diameter of the semicircle at low frequency; a smaller diameter indicates a lower charge
41
42 transfer resistance. **Figure 4g** shows the Nyquist plots of the TiO_2 and NCDs/ TiO_2 photoanodes
43
44 from 100 kHz to 0.1 Hz under simulated solar light illumination (0.3V vs RHE). The prepared
45
46 NCDs/ TiO_2 show a smaller semi-circular diameter compare to TiO_2 under light illumination,
47
48 revealing that the NCDs/ TiO_2 electrode possesses less photo-induced charge transfer resistance in
49
50 the interface of electrode and electrolyte, highlighting the key benefit of NCDs in improving
51
52 charge separation efficiency and enhancing photoelectrochemical activity. Compare with the EIS
53
54
55
56
57
58
59
60

1
2
3 performed under dark conditions, we can tell that the charge transfer resistance of NCDs/TiO₂
4 electrode decreased faster by light illumination compared with pristine TiO₂. This proves that
5 NCDs provided photosensitised electrons to TiO₂ and separated the electron-hole pairs more
6 efficiently, thereby decreasing the impedance under light.⁵⁴ Additionally, the Mott-Schottky (M-
7 S) measured at 10 kHz reveals a higher carrier density after NCDs deposition (**Figure 4h**) from
8 the smaller slope of NCDs/TiO₂ curve.^{50,55} To minimise the effect of surface state capacitance and
9 the double-layer capacitance at the electrode/electrolyte interface, the frequency of the M-S
10 measurements was chosen to be fast enough to limit the effective filling and unfilling of the
11 electrodes' surface state, as well as restrain the building up of double layer capacitance. On that
12 note, even though this analysis is derived from an ideal planar electrode model, the calculation of
13 carrier density for a relative comparison is still reasonable.⁵⁶ Measurements at different frequency
14 (1 kHz and 3 kHz) can be found in **Figure S10**. The carrier density (N_D) can be estimated by the
15 equation:

$$\frac{1}{C^2} = \frac{2}{\varepsilon \varepsilon_0 A^2 e N_D} \left(V - V_{fb} - \frac{k_B T}{e} \right)$$

16
17 Where $e = 1.6 \times 10^{-19} \text{ C}$, $\varepsilon_0 = 8.86 \times 10^{-12} \text{ F m}^{-1}$, $\varepsilon = 55$ for (101) facet anatase TiO₂ with
18 a small amount of rutile,^{55,57} and C is the capacitance. By using these values, we obtain the average
19 donor densities of $8.44 \times 10^{18} \text{ cm}^{-3}$ and $2.67 \times 10^{19} \text{ cm}^{-3}$ for TiO₂ and NCDs/TiO₂
20 electrodes, respectively. The extrapolation of the M-S plot to the x- intercept gives flat potential
21 of the electrode, in which the NCDs modified TiO₂ show a slightly negative potential than that of
22 TiO₂, by 0.1 V, which may due to the hybridised band structure of NCDs and TiO₂ and favours
23 the migration of photoinduced electrons from NCDs to TiO₂.³⁹

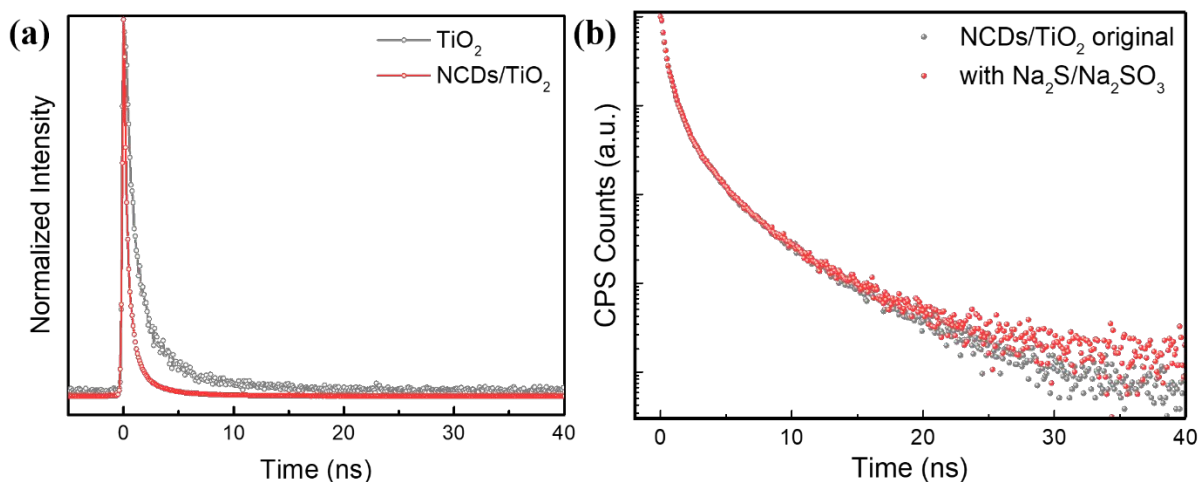


Figure 5 (a) TCSPC decay profile of TiO₂ (grey) and NCDs/TiO₂ (red); (b) decay profiles of NCDs/TiO₂ with (red) and without (grey) the presence of hole scavenger Na₂S/Na₂SO₃. The excitation wavelength for all the experiments is 405 nm, and the emission is recorded at 520 nm.

To further study and gain greater insight into the charge transfer properties in NCDs/TiO₂ heterostructure, Time-correlated Single Photon Counting measurement was performed on pristine TiO₂ and NCDs decorated sample. From **Figure 5a** we can observe a faster photoluminescence (PL) decay after depositing NCDs, which clearly indicate the existence of charge transfer between NCDs and TiO₂, suppressing the radiative charge recombination in TiO₂.⁴³ The PL quenching of the samples were tested in-situ in an electrolyte with the presence of hole scavengers (Na₂S/Na₂SO₃). It is advised that the presence of hole scavengers can effectively react with photogenerated holes and enrich the electrons in a photocatalyst system,⁵⁸ facilitate charge separation and prevent electron-hole recombination, leading to a lower PL and shorter PL lifetime. Comparing the decay profiles of NCDs/TiO₂ with/without hole scavengers in **Figure 5b**, it can be seen that the PL lifetime remained almost identical, suggesting a negligible PL quenching process. In comparison, the PL lifetime of TiO₂ has dramatically decreased from 3.14 ns to 1.75 ns after adding hole scavengers (**Figure S11**). This is probably due to the efficient charge separation in the

1
2
3 NCDs/TiO₂ system, with photogenerated electrons transferred to TiO₂ and holes transported to the
4 surface of NCDs.^{59,60}
5
6

7
8 Combined ultraviolet photoemission spectroscopy (UPS) and photoelectron spectroscopy in air
9 (PESA) techniques provide insights into the electronic structure and energy band positions of the
10 NCDs/TiO₂ materials. The value of ionisation potential of NCD powders from PESA in **Figure**
11 **S12a** was determined to be 5.5 eV ± 0.02 eV, corresponding to the energy of the highest occupied
12 electronic state (HOMO) of NCDs. The Fermi level of NCDs (E_{f1}) was probed directly by Kelvin
13 probe and was determined to be -4.3 eV. The UV/Vis absorption spectrum of NCDs in **Figure S2a**
14 suggests a relatively large energy gap of 3.5 eV, leaving the lowest unoccupied electronic state
15 (LUMO) at -2 eV. However, the excitation-dependent PL of NCDs (**Figure S2b**) indicates
16 individual energy states of NCDs, which allows energy transitions extending up to 500 nm (2.48
17 eV).³¹ The valence band edge and Fermi level (E_{f2}) of TiO₂ from UPS are -7.65 eV and -5.22 eV,
18 respectively (**Figure S12b**), similar to the reported band position of anatase phase TiO₂.^{61,62} The
19 band gap (E_g) was calculated to be 3.21 eV from Tauc plot (**Figure 4b**), from which according to
20 $E_g = E_C - E_V$, the conduction band (CB) edge is estimated to be -4.44 eV, above the H⁺/H₂
21 reduction potential. As to the NCDs/TiO₂, the measured Fermi level (E_{f3}) is -5.16 eV by UPS, in
22 between that of NCDs and TiO₂, consistent with the observation in the PEC Mott-Schottky
23 measurements mentioned previously. A continuous distribution of valence band states is observed
24 up to ~3.6 eV in UPS concerning the Fermi level, indicating there are mid-states existing within
25 the bandgap of the nanocomposite. These states are likely formed at the NCDs/TiO₂ interface and
26 will promote hole transport from the valence band of TiO₂ to the HOMO band of NCDs.⁶³
27 Moreover, the ionization energy of NCDs at 5.5 eV, much smaller than the energy for TiO₂ (7.65
28 eV), clear suggests a transfer of holes from TiO₂ to NCDs.⁶³ To the best of our knowledge this is
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

the first report that directly probes the band positions of carbon dots-TiO₂ photoelectrode in a PEC system for understanding the energy transfer mechanism.

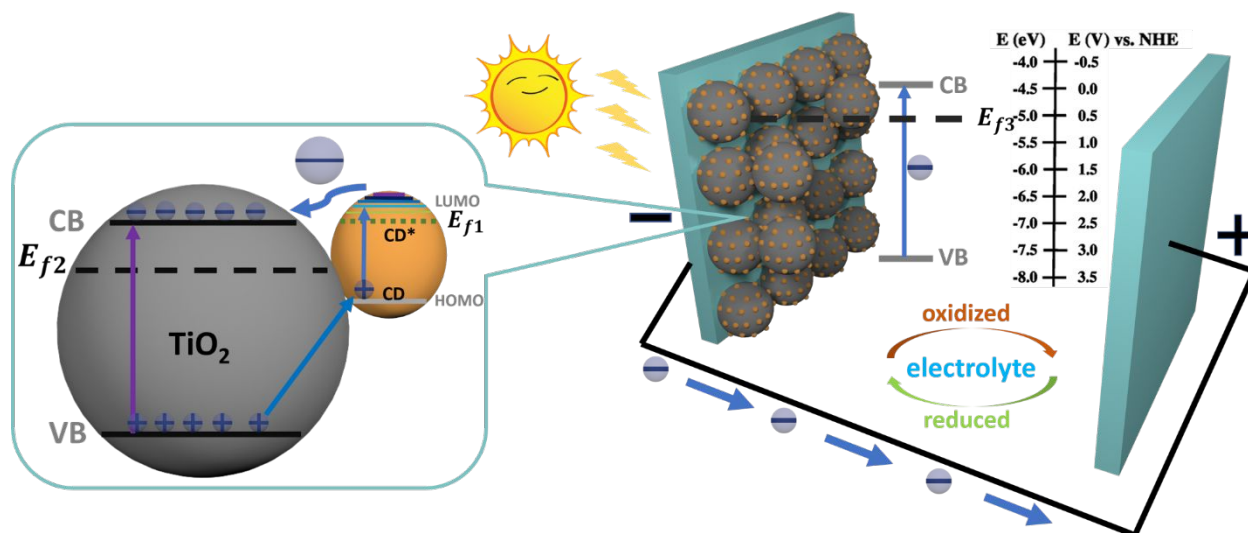


Figure 6 Proposed formation of the heterostructure with band alignments and charge transfer at the surface of TiO₂ and NCDs under light irradiation.

Based on the above results, a schematic diagram of the PEC mechanism is depicted in **Figure 6**. Under full spectrum irradiation, the electrons on the HOMO of NCDs and valence band (VB) of TiO₂ can be effectively excited to the LUMO/CB, respectively. The electrons from the LUMO band of NCDs can then quickly transfer to the CB of the TiO₂ due to its deeper energy level. The holes left in the VB of TiO₂ then transfer to the NCDs, where it can react with the electrolyte for oxidation reactions. The accumulated electrons in TiO₂ would then go into the external circuit to the counter electrode where reduction reactions take place, resulting in a higher measured photocurrent. While under visible light irradiation, the higher photoactivity is induced by obtaining a new absorption band through interfacial charge transfer.⁴⁴ Electrons in NCDs were excited from HOMO band on to LUMO band, where they are effectively transferred through TiO₂ into the circuit under positive bias, resulted in a higher photocurrent response.

1
2
3 Our work has therefore shown that in this hybrid system the energy levels are arranged such that,
4 a photon excites an electron-hole pair on the NCDs with a subsequent electron transfer to the TiO₂,
5 which would then be transferred to counter electrode. This leaves a hole in the valence band of the
6 NCDs residing at -5.5 eV which provides a site for electron transfer from OH⁻, which is the electron
7 donor (D) in the electrolyte solution. The conversion of D⁺ from D with NCDs/TiO₂ as
8 photocatalysts under illumination produces the photocurrent, completing the PEC circuit.
9

17 **3.Conclusions**

19 In summary, a facile solvothermal method was employed to synthesise nanoscale NCDs with
20 good optical and PEC response in the UV-visible range. This type of carbon dots can be applied
21 as a photosensitizer for improving the PEC activity of TiO₂ and used as a model system to
22 understand the fundamental mechanism of sensitisation using NCDs. The obtained NCDs/TiO₂
23 electrode exhibits a higher photocurrent compared to the pristine TiO₂, with an even greater
24 enhancement under visible light illumination. A variety of complementary techniques such as HR-
25 STEM, EELS, UV-Vis absorption, EIS, M-S, TCSPC and UPS were performed to investigate the
26 optoelectronic properties, photo-induced charge transfer and band structure of the hybrid. The
27 results reveal that the improved PEC activity for the NCDs/TiO₂ arises from the synergistic effect
28 of NCDs combined with TiO₂, which expand the light response into visible range as well as form
29 type II heterojunction at the interface with well-resolved band position probing which have been
30 reported for the first time. We show here the charge transfer process between NCDs and TiO₂,
31 with in-depth analysis of the energy transitions to develop a comprehensive fundamental
32 understanding on the favoured role of NCDs in the photoelectrocatalytic reactions. The importance
33 of combining structural, photophysical and electrochemical assays on systematically improve the
34 charge transfer process between carbon dots and their catalyst counterparts is also addressed here.
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 Future work will focus on tuning the carbon dots properties and optimising the hybridisation with
4
5 other photoelectrocatalytic systems or z-schemes for enhanced photocatalytic performances.
6
7
8
9

10 **ASSOCIATED CONTENT**

11 12 13 **Supporting Information**

14
15 The supporting Information is available free of charge on the ACS Publications website.
16
17

18 More characterizations on NCDs/TiO₂'s morphology and chemical/physical properties. (PDF)
19
20

21 **AUTHOR INFORMATION**

22 23 24 **Corresponding Author**

25
26
27 *E-mail: m.titirici@imperial.ac.uk
28
29

30 **Author Contributions**

31
32 The manuscript was written through contributions of all authors. All authors have given approval
33 to the final version of the manuscript. HL produced the NCDs/TiO₂ materials and performed all
34 the basic characteristic techniques; SD helped with the TAS and TCSPC measurements; MD, JSK
35 measured the fermi level while MAS, PS and OF helped with UPS and PESA analysis; HL, QG,
36 YF, ABJ, XW and MMT co-wrote the paper. All authors have contributed to revise the manuscript.
37
38

39 **Notes**

40
41 The authors declare no competing financial interest.
42
43
44

45 **ACKNOWLEDGMENT**

46
47
48 HL and QG thanks the Chinese government for the award of CSC scholarships, and Dr Enrico
49 Salvadori for the EPR measurement. SD is grateful for financial support by Edinburgh Instruments.
50
51 This work is part-funded by the European Regional Development Fund through the Welsh
52
53 Government. We thank the Diamond Light Source for access and support in the use of the electron
54
55
56
57
58
59
60

1
2
3 Physical Science Imaging Centre (Instrument E01 proposal MG22447) that contributed to the
4 results presented here. PS acknowledges financial support from the Agence Nationale de la
5 Recherche through the Labex projects CSC (ANR-10-LABX-0026 CSC) within the
6 Investissement d'avenir program (ANR-10-120 IDEX-0002-02), by the International Center for
7 Frontier Research in Chemistry (icFRC). OF acknowledges support from the Royal Society
8 through a University Research Fellowship (UF140372). XW thanks the National Natural Science
9 Foundation of China (21861130353).

20 REFERENCES

- 21
22 (1) Fujishima, A., & Honda, K. Electrochemical Photolysis of Water One and Two-
23 Dimensional Structure of Poly (L-Alanine) Shown by Specific Heat Measurements at Low.
24 *Nature* **1972**, *238*, 37–38.
25
26
27
28
29
30 (2) Zhao, L.; Chen, X.; Wang, X.; Zhang, Y.; Wei, W.; Sun, Y.; Antonietti, M.; Titirici, M. M.
31 One-Step Solvothermal Synthesis of a Carbon @TiO₂ Dyade Structure Effectively
32 Promoting Visible-Light Photocatalysis. *Adv. Mater.* **2010**, *22* (30), 3317–3321.
33
34
35
36
37
38 (3) Yoo, I. han; Kalanur, S. S.; Seo, H. A Nanoscale p–n Junction Photoelectrode Consisting
39 of an NiO_x Layer on a TiO₂/CdS Nanorod Core-Shell Structure for Highly Efficient Solar
40 Water Splitting. *Appl. Catal. B Environ.* **2019**, *250* (February), 200–212.
41
42
43
44
45
46 (4) Tada, H.; Mitsui, T.; Kiyonaga, T.; Akita, T.; Tanaka, K. All-Solid-State Z-Scheme in CdS–
47 Au–TiO₂ Three-Component Nanojunction System. *Nat. Mater.* **2006**, *5* (10), 782–786.
48
49
50
51 (5) Zhao, H.; Hu, Z.; Liu, J.; Li, Y.; Wu, M.; Van Tendeloo, G.; Su, B. L. Blue-Edge Slow
52 Photons Promoting Visible-Light Hydrogen Production on Gradient Ternary 3DOM TiO₂-
53 Au-CdS Photonic Crystals. *Nano Energy* **2018**, *47* (December 2017), 266–274.
54
55
56
57
58
59
60

- 1
2
3 (6) Sant, P. A.; Kamat, P. V. Interparticle Electron Transfer between Size-Quantized CdS and
4 TiO₂ Semiconductor Nanoclusters. *Phys. Chem. Chem. Phys.* **2002**, *4* (2), 198–203.
5
6
7
8
9 (7) Lee, Y.-L.; Chi, C.-F.; Liao, S.-Y. CdS/CdSe Co-Sensitized TiO₂ Photoelectrode for
10 Efficient Hydrogen Generation in a Photoelectrochemical Cell. *Chem. Mater.* **2010**, *22* (3),
11 922–927.
12
13
14
15
16 (8) Zhang, F.; Zhang, C.-L.; Wang, W.-N.; Cong, H.-P.; Qian, H.-S. Titanium
17 Dioxide/Upconversion Nanoparticles/Cadmium Sulfide Nanofibers Enable Enhanced Full-
18 Spectrum Absorption for Superior Solar Light Driven Photocatalysis. *ChemSusChem* **2016**,
19 *9* (12), 1449–1454.
20
21
22
23
24
25
26 (9) Xiong, Z.; Luo, Y.; Zhao, Y.; Zhang, J.; Zheng, C.; Wu, J. C. S. Synthesis, Characterization
27 and Enhanced Photocatalytic CO₂ Reduction Activity of Graphene Supported TiO₂
28 Nanocrystals with Coexposed {001} and {101} Facets. *Phys. Chem. Chem. Phys.* **2016**, *18*
29 (19), 13186–13195.
30
31
32
33
34
35
36 (10) Lu, Y.; Cheng, X.; Tian, G.; Zhao, H.; He, L.; Hu, J.; Wu, S. M.; Dong, Y.; Chang, G. G.;
37 Lenaerts, S.; Siffert, S.; Van Tendeloo, G.; Li, Z. F.; Xu, L. L.; Yang, X. Y.; Su, B. L.
38 Hierarchical CdS/m-TiO₂/G Ternary Photocatalyst for Highly Active Visible Light-
39 Induced Hydrogen Production from Water Splitting with High Stability. *Nano Energy* **2018**,
40 *47* (September 2017), 8–17.
41
42
43
44
45
46
47
48 (11) Yu, H.; Zhao, Y.; Zhou, C.; Shang, L.; Peng, Y.; Cao, Y.; Wu, L.-Z.; Tung, C.-H.; Zhang,
49 T. Carbon Quantum Dots/TiO₂ Composites for Efficient Photocatalytic Hydrogen
50 Evolution. *J. Mater. Chem. A* **2014**, *2* (10), 3344.
51
52
53
54
55
56
57
58
59
60

- 1
2
3 (12) Tian, J.; Leng, Y.; Zhao, Z.; Xia, Y.; Sang, Y.; Hao, P.; Zhan, J.; Li, M.; Liu, H. Carbon
4 Quantum Dots/Hydrogenated TiO₂ Nanobelt Heterostructures and Their Broad Spectrum
5 Photocatalytic Properties under UV, Visible, and near-Infrared Irradiation. *Nano Energy*
6 **2015**, *11*, 419–427.
7
8
9
10
11
12
13 (13) Chen, P.; Wang, F.; Chen, Z. F.; Zhang, Q.; Su, Y.; Shen, L.; Yao, K.; Liu, Y.; Cai, Z.; Lv,
14 W.; Liu, G. Study on the Photocatalytic Mechanism and Detoxicity of Gemfibrozil by a
15 Sunlight-Driven TiO₂/Carbon Dots Photocatalyst: The Significant Roles of Reactive
16 Oxygen Species. *Appl. Catal. B Environ.* **2017**, *204*, 250–259.
17
18
19
20
21
22
23 (14) Wang, Q.; Huang, J.; Sun, H.; Zhang, K.-Q.; Lai, Y. Uniform Carbon Dots@TiO₂ Nanotube
24 Arrays with Full Spectrum Wavelength Light Activation for Efficient Dye Degradation and
25 Overall Water Splitting. *Nanoscale* **2017**, *9*, 16046–16058.
26
27
28
29
30
31 (15) Liang, Z.; Hou, H.; Fang, Z.; Gao, F.; Wang, L.; Chen, D.; Yang, W. Hydrogenated TiO₂
32 Nanorod Arrays Decorated with Carbon Quantum Dots toward Efficient
33 Photoelectrochemical Water Splitting. *ACS Appl. Mater. Interfaces* **2019**, *11* (21), 19167–
34 19175.
35
36
37
38
39
40
41 (16) Shi, W.; Guo, F.; Zhu, C.; Wang, H.; Li, H.; Huang, H.; Liu, Y.; Kang, Z. Carbon Dots
42 Anchored on Octahedral CoO as a Stable Visible-Light-Responsive Composite
43 Photocatalyst for Overall Water Splitting. *J. Mater. Chem. A* **2017**, *5* (ii), 19800–19807.
44
45
46
47
48
49 (17) Martins, N. C. T.; Ângelo, J.; Girão, A. V.; Trindade, T.; Andrade, L.; Mendes, A. N-Doped
50 Carbon Quantum Dots/TiO₂ Composite with Improved Photocatalytic Activity. *Appl.*
51 *Catal. B Environ.* **2016**, *193*, 67–74.
52
53
54
55
56
57
58
59
60

- 1
2
3 (18) Wang, B.; Deng, Z.; Fu, X.; Li, Z. MoS₂/CQDs Obtained by Photoreduction for Assembly
4 of a Ternary MoS₂/CQDs/ZnIn₂S₄ Nanocomposite for Efficient Photocatalytic Hydrogen
5 Evolution under Visible Light. *J. Mater. Chem. A* **2018**, *6* (40), 19735–19742.
6
7
8
9
10
11 (19) Feng, J.; Liu, G.; Yuan, S.; Ma, Y. Influence of Functional Groups on Water Splitting in
12 Carbon Nanodots and Graphitic Carbon Nitride Composites: A Theoretical Mechanism
13 Study. *Phys. Chem. Chem. Phys.* **2017**, *19*, 4997–5003.
14
15
16
17
18 (20) Luo, H.; Papaioannou, N.; Salvadori, E.; Roessler, M. M.; Ploenes, G.; Eck, E. R. H.;
19 Tanase, L. C.; Feng, J.; Sun, Y.; Yang, Y.; Danaie, M.; Belen Jorge, A.; Sapelkin, A.;
20 Durrant, J.; Dimitrov, S. D.; Titirici, M. Manipulating the Optical Properties of Carbon Dots
21 by Fine-Tuning Their Structural Features. *ChemSusChem* **2019**, *12* (19), 4335–4335.
22
23
24
25
26
27
28 (21) Shi, R.; Li, Z.; Yu, H.; Shang, L.; Zhou, C.; Waterhouse, G. I. N.; Wu, L. Z.; Zhang, T.
29 Effect of Nitrogen Doping Level on the Performance of N-Doped Carbon Quantum
30 Dot/TiO₂ Composites for Photocatalytic Hydrogen Evolution. *ChemSusChem* **2017**, *10*
31 (22), 4650–4656.
32
33
34
35
36
37
38 (22) Yan, M.; Hua, Y.; Zhu, F.; Gu, W.; Jiang, J.; Shen, H.; Shi, W. Fabrication of Nitrogen
39 Doped Graphene Quantum Dots-BiOI/MnNb₂O₆ p-n Junction Photocatalysts with
40 Enhanced Visible Light Efficiency in Photocatalytic Degradation of Antibiotics. *Appl.*
41 *Catal. B Environ.* **2017**, *202*, 518–527.
42
43
44
45
46
47
48 (23) Sk, M. A.; Ananthanarayanan, A.; Huang, L.; Lim, K. H.; Chen, P. Revealing the Tunable
49 Photoluminescence Properties of Graphene Quantum Dots. *J. Mater. Chem. C* **2014**, *2* (34),
50 6954–6960.
51
52
53
54
55
56
57
58
59
60

- 1
2
3 (24) Otyepka, M.; Kalytchuk, S.; Rogach, A. L.; Zbořil, R.; Sudolská, M.; Nachtigallová, D.;
4
5 Holá, K. Graphitic Nitrogen Triggers Red Fluorescence in Carbon Dots. *ACS Nano* **2017**,
6
7 *11* (12), 12402–12410.
8
9
10
11 (25) Zhang, Y. Q.; Ma, D. K.; Zhang, Y. G.; Chen, W.; Huang, S. M. N-Doped Carbon Quantum
12
13 Dots for TiO₂-Based Photocatalysts and Dye-Sensitized Solar Cells. *Nano Energy* **2013**, *2*
14
15 (5), 545–552.
16
17
18 (26) Liang, Z.; Hou, H.; Fang, Z.; Gao, F.; Wang, L.; Chen, D.; Yang, W. Hydrogenated TiO₂
19
20 Nanorod Arrays Decorated with Carbon Quantum Dots toward Efficient
21
22 Photoelectrochemical Water Splitting. *ACS Appl. Mater. Interfaces* **2019**, *11* (21), 19167–
23
24 19175.
25
26
27
28 (27) Martindale, B. C. M.; Hutton, G. A. M.; Caputo, C. A.; Prantl, S.; Godin, R.; Durrant, J. R.;
29
30 Reisner, E. Enhancing Light Absorption and Charge Transfer Efficiency in Carbon Dots
31
32 through Graphitization and Core Nitrogen Doping. *Angew. Chemie - Int. Ed.* **2017**, *56*,
33
34 6459–6463.
35
36
37
38 (28) Hu, R.; Li, L.; Jin, W. J. Controlling Speciation of Nitrogen in Nitrogen-Doped Carbon Dots
39
40 by Ferric Ion Catalysis for Enhancing Fluorescence. *Carbon N. Y.* **2017**, *111*, 133–141.
41
42
43
44 (29) Xie, S.; Su, H.; Wei, W.; Li, M.; Tong, Y.; Mao, Z. Remarkable Photoelectrochemical
45
46 Performance of Carbon Dots Sensitized TiO₂ under Visible Light Irradiation. *J. Mater.*
47
48 *Chem. A* **2014**, *2* (39), 16365–16368.
49
50
51
52 (30) Yang, Y.; Cui, J.; Zheng, M.; Hu, C.; Tan, S.; Xiao, Y.; Yang, Q.; Liu, Y. One-Step
53
54 Synthesis of Amino-Functionalized Fluorescent Carbon Nanoparticles by Hydrothermal
55
56
57
58
59
60

- 1
2
3 Carbonization of Chitosan. *Chem. Commun.* **2012**, *48*, 380–382.
4
5
6
7 (31) Zhang, D.-W.; Papaioannou, N.; David, N. M.; Luo, H.; Gao, H.; Tanase, L. C.; Degoussé,
8 T.; Samori, P.; Sapelkin, A.; Fenwick, O.; Titirici, M.-M.; Krause, S. Photoelectrochemical
9 Response of Carbon Dots (CDs) Derived from Chitosan and Their Use in Electrochemical
10 Imaging. *Mater. Horizons* **2018**, *5*, 423–428.
11
12
13
14
15
16 (32) Marinovic, A.; Kiat, L. S.; Dunn, S.; Titirici, M. M.; Briscoe, J. Carbon-Nanodot Solar Cells
17 from Renewable Precursors. *ChemSusChem* **2017**, *10* (5), 1004–1013.
18
19
20
21
22 (33) Shu, C.-K. Degradation Products Formed from Glucosamine in Water. *J. Agric. Food*
23 *Chem.* **1998**, *46* (3), 1129–1131.
24
25
26
27 (34) Ortega-Liebana, M. C.; Chung, N. X.; Limpens, R.; Gomez, L.; Hueso, J. L.; Santamaria,
28 J.; Gregorkiewicz, T. Uniform Luminescent Carbon Nanodots Prepared by Rapid Pyrolysis
29 of Organic Precursors Confined within Nanoporous Templating Structures. *Carbon N. Y.*
30 **2017**, *117*, 437–446.
31
32
33
34
35
36
37 (35) Yang, M.; Li, B.; Zhong, K.; Lu, Y. Photoluminescence Properties of N-Doped Carbon Dots
38 Prepared in Different Solvents and Applications in PH Sensing. *J. Mater. Sci.* **2018**, *53*,
39 2424–2433.
40
41
42
43
44
45 (36) Santos, C. I. M.; Mariz, I. F. A.; Pinto, S. N.; Gonçalves, G.; Bdikin, I.; Marques, P. A. A.
46 P.; Neves, M. G. P. M. S.; Martinho, J. M. G.; Maçôas, E. M. S. Selective Two-Photon
47 Absorption in Carbon Dots: A Piece of the Photoluminescence Emission Puzzle. *Nanoscale*
48 **2018**, *10* (26), 12505–12514.
49
50
51
52
53
54
55 (37) Strauss, V.; Margraf, J. T.; Dolle, C.; Butz, B.; Nacken, T. J.; Bauer, W.; Peukert, W.;


- 1
2
3 Spiecker, E.; Clark, T.; Guldi, D. M. Carbon Nanodots – Towards a Comprehensive
4 Understanding of Their Photoluminescence. *J. Am. Chem. Soc.* **2014**, *49*, 17308–17316.
5
6
7
8
9 (38) Sudolská, M.; Dubecký, M.; Sarkar, S.; Reckmeier, C. J.; Zbořil, R.; Rogach, A. L.;
10 Otyepka, M. Nature of Absorption Bands in Oxygen-Functionalized Graphitic Carbon Dots.
11 *J. Phys. Chem. C* **2015**, *119*, 13369–13373.
12
13
14
15
16 (39) Li, Y.; Li, P.; Wang, J.; Yang, Y.; Yao, W.; Wei, Z.; Wu, J.; Yan, X.; Xu, X.; Liu, Y.; Zhu,
17 Y. Water Soluble Graphitic Carbon Nitride with Tunable Fluorescence for Boosting Broad-
18 Response Photocatalysis. *Appl. Catal. B Environ.* **2018**, *225* (November 2017), 519–529.
19
20
21
22
23
24 (40) Sahu, S.; Behera, B.; Maiti, T. K.; Mohapatra, S. Simple One-Step Synthesis of Highly
25 Luminescent Carbon Dots from Orange Juice: Application as Excellent Bio-Imaging
26 Agents. *Chem. Commun.* **2012**, *48*, 8835–8837.
27
28
29
30
31
32 (41) Guin, J. P.; Guin, S. K.; Debnath, T.; Ghosh, H. N. Chemically Clean Single-Step Oxido-
33 Reductive Synthesis of Green Luminescent Graphene Quantum Dots as Impending
34 Electrocatalyst. *Carbon N. Y.* **2016**, *109*, 517–528.
35
36
37
38
39 (42) Shi, X. F.; Xia, X. Y.; Cui, G. W.; Deng, N.; Zhao, Y. Q.; Zhuo, L. H.; Tang, B. Multiple
40 Exciton Generation Application of PbS Quantum Dots in ZnO@PbS/Graphene Oxide for
41 Enhanced Photocatalytic Activity. *Appl. Catal. B Environ.* **2015**, *163*, 123–128.
42
43
44
45
46
47 (43) Shi, X.; Kim, S.; Fujitsuka, M.; Majima, T. In Situ Observation of NiS Nanoparticles
48 Depositing on Single TiO₂ Mesocrystal for Enhanced Photocatalytic Hydrogen Evolution
49 Activity. *Appl. Catal. B Environ.* **2019**.
50
51
52
53
54
55 (44) Lee, K.; Yoon, H.; Ahn, C.; Park, J.; Jeon, S. Strategies to Improve the Photocatalytic
56
57
58
59
60

- 1
2
3 Activity of TiO₂: 3D Nanostructuring and Heterostructuring with Graphitic Carbon
4
5 Nanomaterials. *Nanoscale* **2019**, *11* (15), 7025–7040.
6
7
8
9 (45) Chen, Z.; Dinh, H. N.; Miller, E. *Photoelectrochemical Water Splitting: Standards,*
10
11 *Experimental Methods, and Protocols*; Springer, 2013.
12
13
14 (46) Wang, H.; An, T.; Selloni, A. Effect of Reducible Oxide-Metal Cluster Charge Transfer on
15
16 the Structure and Reactivity of Adsorbed Au and Pt Atoms and Clusters on Anatase TiO₂.
17
18 *J. Chem. Phys.* **2017**, *146* (18), 184703.
19
20
21
22 (47) Nie, Y. C.; Yu, F.; Wang, L. C.; Xing, Q. J.; Liu, X.; Pei, Y.; Zou, J. P.; Dai, W. L.; Li, Y.;
23
24 Suib, S. L. Photocatalytic Degradation of Organic Pollutants Coupled with Simultaneous
25
26 Photocatalytic H₂ Evolution over Graphene Quantum Dots/Mn-N-TiO₂/g-C₃N₄
27
28 Composite Catalysts: Performance and Mechanism. *Appl. Catal. B Environ.* **2018**, *227*
29
30 (October 2017), 312–321.
31
32
33
34 (48) Tian, J.; Leng, Y.; Zhao, Z.; Xia, Y.; Sang, Y.; Hao, P.; Zhan, J.; Li, M.; Liu, H. Carbon
35
36 Quantum Dots/Hydrogenated TiO₂nanobelt Heterostructures and Their Broad Spectrum
37
38 Photocatalytic Properties under UV, Visible, and near-Infrared Irradiation. *Nano Energy*
39
40 **2015**, *11*, 419–427.
41
42
43
44 (49) Yu, L.; Shao, Y.; Li, D. Direct Combination of Hydrogen Evolution from Water and
45
46 Methane Conversion in a Photocatalytic System over Pt/TiO₂. *Appl. Catal. B Environ.*
47
48 **2017**, *204*, 216–223.
49
50
51
52 (50) Xu, Y.; Zhang, C.; Zhang, L.; Zhang, X.; Yao, H.; Shi, J. Pd-Catalyzed Instant
53
54 Hydrogenation of TiO₂ with Enhanced Photocatalytic Performance. *Energy Environ. Sci.*
55
56
57
58
59
60

- 1
2
3 **2016**, *9* (7), 2410–2417.
4
5
6
7 (51) D’Angelo, D.; Bongiorno, C.; Amato, M.; Deretzis, I.; La Magna, A.; Fazio, E.; Scalese, S.
8 Oxygen Functionalities Evolution in Thermally Treated Graphene Oxide Featured by EELS
9 and DFT Calculations. *J. Phys. Chem. C* **2017**, *121* (9), 5408–5414.
10
11
12
13
14 (52) Rajender, G.; Kumar, J.; Giri, P. K. Interfacial Charge Transfer in Oxygen Deficient TiO₂-
15 Graphene Quantum Dot Hybrid and Its Influence on the Enhanced Visible Light
16 Photocatalysis. *Appl. Catal. B Environ.* **2018**, *224* (October 2017), 960–972.
17
18
19
20
21
22 (53) Raziq, F.; Sun, L.; Wang, Y.; Zhang, X.; Humayun, M.; Ali, S.; Bai, L.; Qu, Y.; Yu, H.;
23 Jing, L. Synthesis of Large Surface-Area g-C₃N₄ Comodified with MnO_x and Au-TiO₂ as
24 Efficient Visible-Light Photocatalysts for Fuel Production. *Adv. Energy Mater.* **2018**, *8* (3),
25 2–11.
26
27
28
29
30
31
32 (54) Tzeng, W. J.; Wu, M. L.; Lin, L. J.; Chang, H. Y. Chalcogenide Photosensitized Titania
33 Nanotube Arrays. *J. Alloys Compd.* **2015**, *651* (December 2015), 483–489.
34
35
36
37 (55) Goossens, A.; Schoonman, J. Mott-Schottky Analysis of Nanometer-Scale. *J. Electrochem.*
38 *Soc.* **1997**, *144* (5), 1723–1727.
39
40
41
42 (56) Luo, Z.; Wang, T.; Zhang, J.; Li, C.; Li, H.; Gong, J. Dendritic Hematite Nanoarray
43 Photoanode Modified with a Conformal Titanium Dioxide Interlayer for Effective Charge
44 Collection. *Angew. Chemie - Int. Ed.* **2017**, *56* (42), 12878–12882.
45
46
47
48
49
50 (57) Kim, J. Y.; Jung, H. S.; No, J. H.; Kim, J. R.; Hong, K. S. Influence of Anatase-Rutile Phase
51 Transformation on Dielectric Properties of Sol-Gel Derived TiO₂ Thin Films. *J.*
52 *Electroceramics* **2006**, *16* (4), 447–451.
53
54
55
56
57
58
59
60

- 1
2
3 (58) Kudo, A.; Miseki, Y. Heterogeneous Photocatalyst Materials for Water Splitting. *Chem.*
4
5 *Soc. Rev.* **2009**, *38* (1), 253–278.
6
7
8 (59) Ma, Z.; Zhang, Y.-L.; Wang, L.; Ming, H.; Li, H.; Zhang, X.; Wang, F.; Liu, Y.; Kang, Z.;
9
10 Lee, S.-T. Bioinspired Photoelectric Conversion System Based on Carbon-Quantum-Dot-
11
12 Doped Dye–Semiconductor Complex. *ACS Appl. Mater. Interfaces* **2013**, *5* (11), 5080–
13
14 5084.
15
16
17 (60) Liu, R.; Huang, H.; Li, H.; Liu, Y.; Zhong, J.; Li, Y.; Zhang, S.; Kang, Z. Metal Nanoparticle
18
19 / Carbon Quantum Dot Composite as Photocatalyst for High Efficiency Cyclohexane
20
21 Oxidation. *Acs Catal.* **2014**, *4*, 328–336.
22
23
24
25 (61) Scanlon, D. O.; Dunnill, C. W.; Buckeridge, J.; Shevlin, S. A.; Logsdail, A. J.; Woodley, S.
26
27 M.; Catlow, C. R. A.; Powell, M. J.; Palgrave, R. G.; Parkin, I. P.; Watson, G. W.; Keal, T.
28
29 W.; Sherwood, P.; Walsh, A.; Sokol, A. A. Band Alignment of Rutile and Anatase TiO₂.
30
31 *Nat. Mater.* **2013**, *12* (9), 798–801.
32
33
34
35 (62) Kashiwaya, S.; Morasch, J.; Streibel, V.; Toupance, T.; Jaegermann, W.; Klein, A. The
36
37 Work Function of TiO₂. *Surfaces* **2018**, *1* (1), 73–89.
38
39
40
41 (63) Saha, A.; Moya, A.; Kahnt, A.; Iglesias, D.; Marchesan, S.; Wannemacher, R.; Prato, M.;
42
43 Vilatela, J. J.; Guldi, D. M. Interfacial Charge Transfer in Functionalized Multi-Walled
44
45 Carbon Nanotube@TiO₂ Nanofibres. *Nanoscale* **2017**, *9* (23), 7911–7921.
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Table of Contents

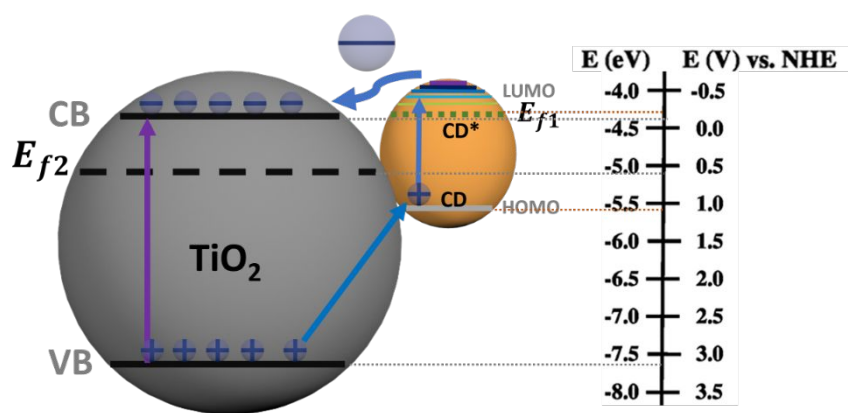

Type II heterojunction with well-resolved band positions

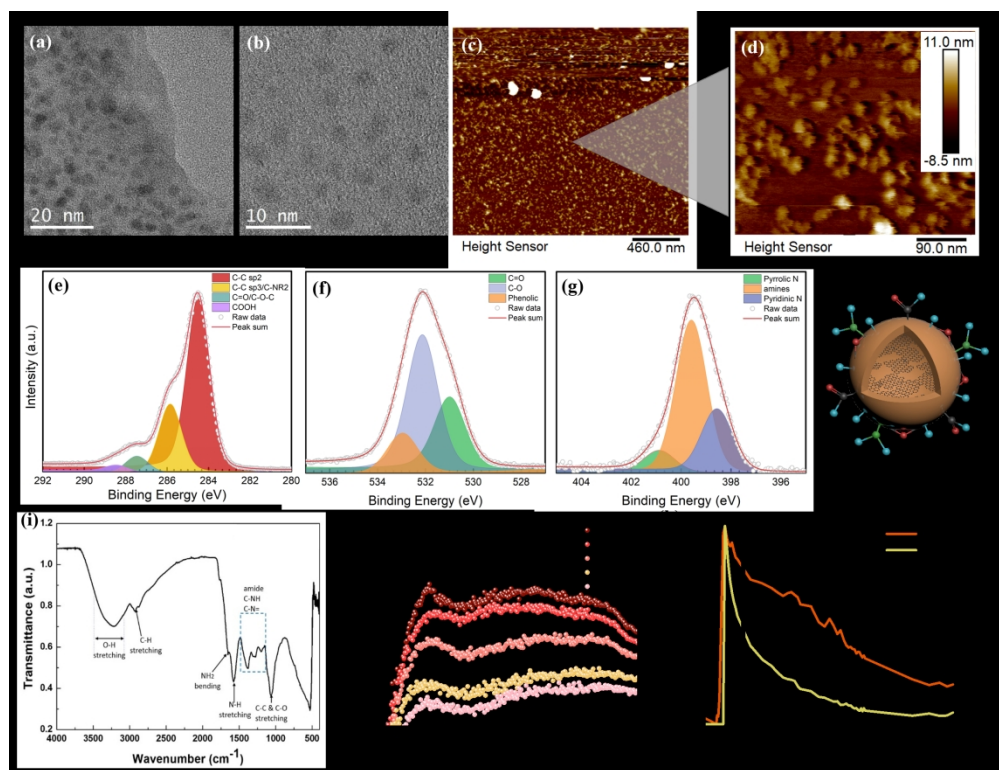


Figure 1 Structural features of as-prepared NCDs: TEM (a) and HR-TEM (b) images; (c) an overview AFM image on mica substrate (Z scale -6.0 to 7.9 nm) and (d) high-resolution scanned image; XPS spectra: (e) C 1s, (f) O 1s, (g) N 1s and corresponding FTIR (i) spectrum; (h) a schematic structure based on the characterizations (atoms in red: O, green: N and blue: H); (j) fs-TAS spectra at different time delays and (k) normalized fs-TAS kinetics of NCDs and non-doped CDs measured at 500 nm, samples were excited at 375 nm.

464x353mm (150 x 150 DPI)

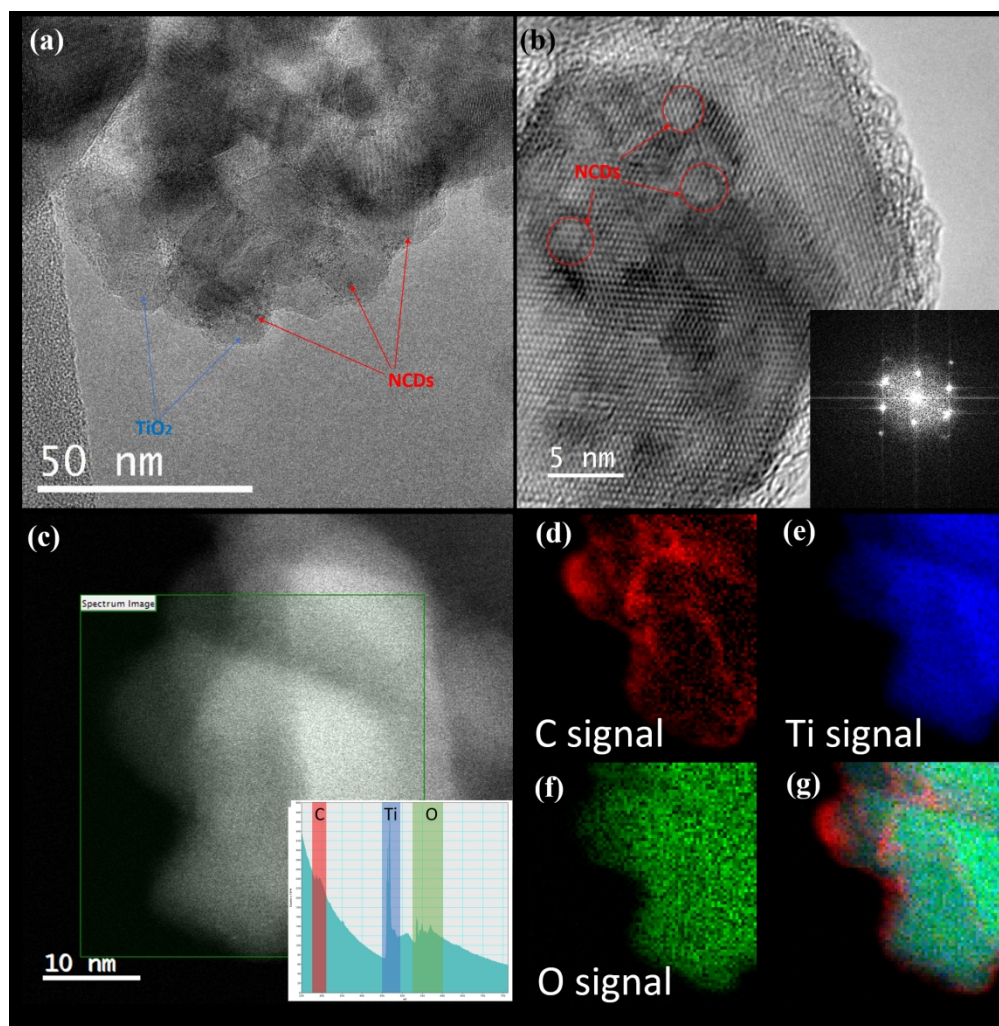


Figure 2 TEM (a) and HR-TEM (b) of NCDs/TiO₂ (insert is the FFT patterns); (c) HAADF image of NCDs/TiO₂ and corresponding EELS spectra (inserted). The single element maps derived from the spectra: (d) C signal, (e) Ti signal, (f) O signal and (g) colour mix (red: C, blue: Ti, green: O).

373x380mm (150 x 150 DPI)

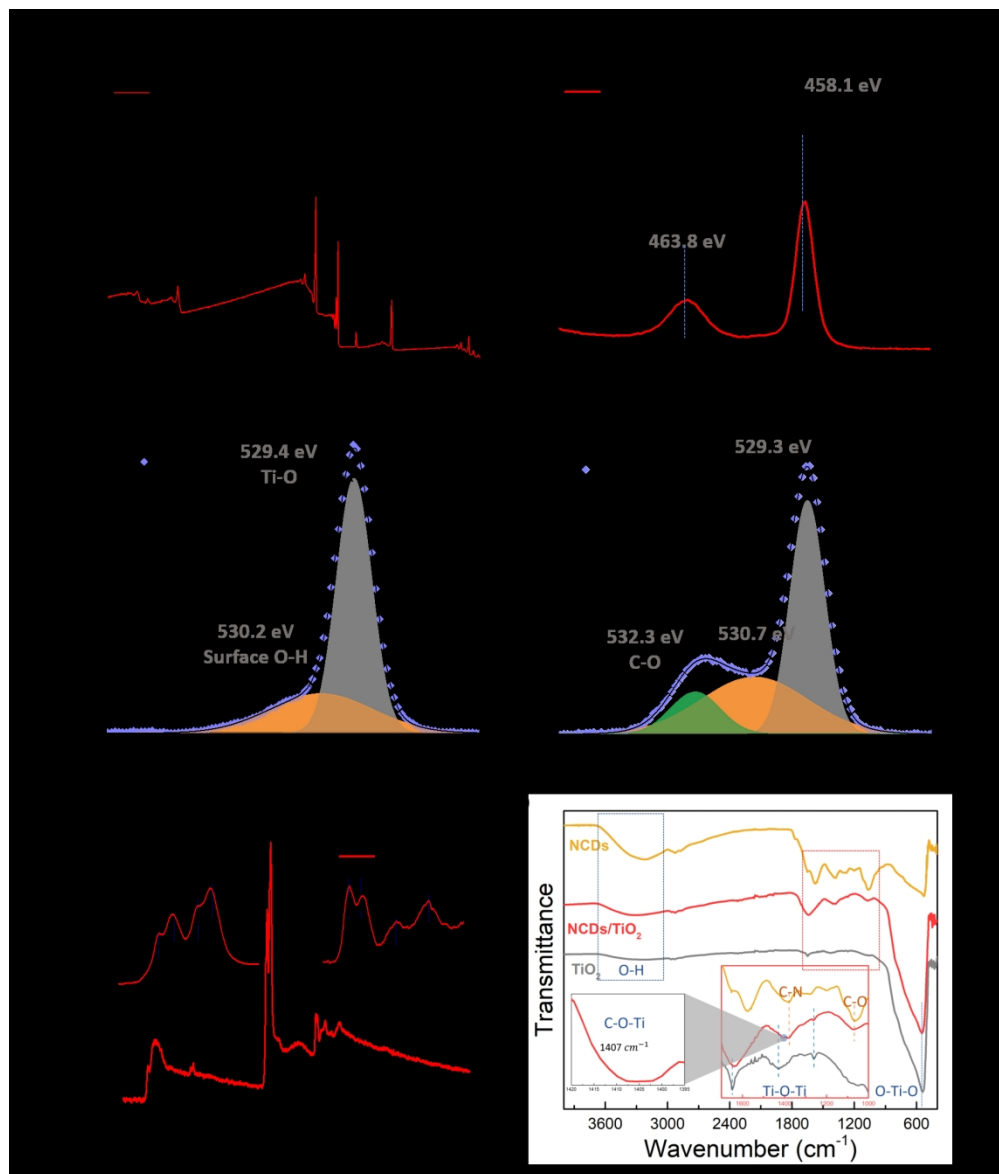


Figure 3 Comparison of XPS survey spectra (a) and corresponding core level spectra (b) Ti 2p of the TiO₂ and NCDs/TiO₂ films; O 1s spectra of (c) TiO₂ and (d) NCDs/TiO₂. (e) EELS spectra of TiO₂ (black) and NCDs/TiO₂ (red) and (f) FTIR signals.

313x366mm (150 x 150 DPI)

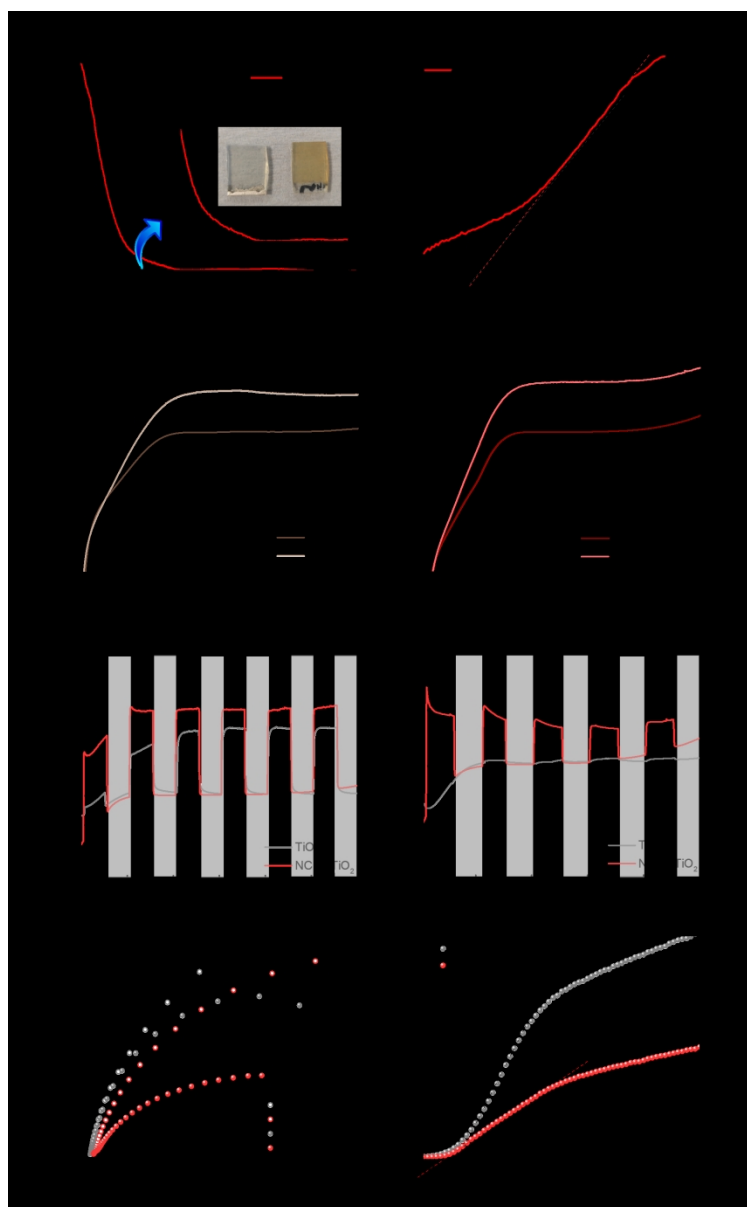


Figure 4 optoelectronic properties of TiO₂ and NCDs/TiO₂ films: (a) UV-Vis absorption (inserted are the digital pictures of the films: left: TiO₂, right: NCDs/TiO₂); (b) tauc plot of TiO₂ and NCDs/TiO₂ with indirect band gap; LSV curves of (c) TiO₂ and (d) NCDs/TiO₂ under dark and light conditions; the chopped photocurrent response of the two samples under (e) full spectrum and (f) visible light ($\lambda > 420$ nm) illumination; (g) EIS Nyquist plots under simulated solar light illumination (100 kHz – 0.1 Hz, 0.3V vs. RHE, 100 mW cm⁻²) and (h) Mott-Schottky plots with 10 kHz frequency under dark condition at equilibrium.

317x506mm (150 x 150 DPI)

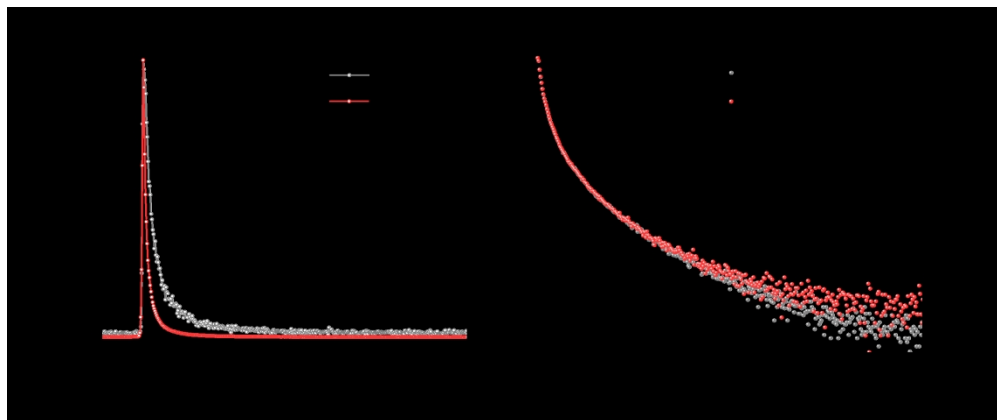


Figure 5 (a) TCSPC decay profile of TiO₂ (grey) and NCDs/TiO₂ (red); (b) decay profiles of NCDs/TiO₂ with (red) and without (grey) the presence of hole scavenger Na₂S/Na₂SO₃. The excitation wavelength for all the experiments is 405 nm, and the emission is recorded at 520 nm.

423x176mm (150 x 150 DPI)

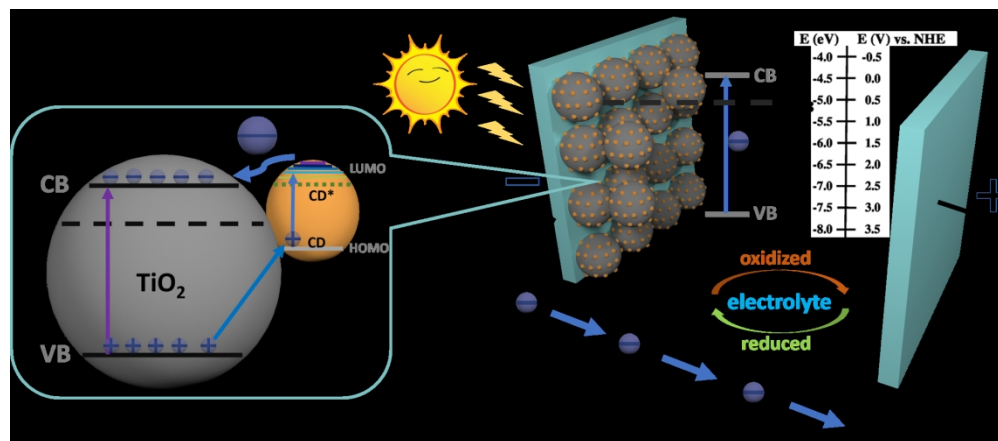


Figure 6 Proposed formation of the heterostructure with band alignments and charge transfer at the surface of TiO₂ and NCDs under light irradiation.

353x154mm (150 x 150 DPI)