



HAL
open science

Dy 3+ White Light Emission Can Be Finely Controlled by Tuning the First Coordination Sphere of Ga 3+ /Dy 3+ Metallocrown Complexes

Svetlana Eliseeva, Elvin Salerno, Beatriz Lopez Bermudez, Stephane Petoud,
Vincent Pecoraro

► **To cite this version:**

Svetlana Eliseeva, Elvin Salerno, Beatriz Lopez Bermudez, Stephane Petoud, Vincent Pecoraro. Dy 3+ White Light Emission Can Be Finely Controlled by Tuning the First Coordination Sphere of Ga 3+ /Dy 3+ Metallocrown Complexes. *Journal of the American Chemical Society*, 2020, 142 (38), pp.16173-16176. 10.1021/jacs.0c07198 . hal-02975958

HAL Id: hal-02975958

<https://hal.science/hal-02975958v1>

Submitted on 16 Nov 2020

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Dy³⁺ white light emission can be finely controlled by tuning the first coordination sphere of Ga³⁺/Dy³⁺ metallacrown complexes

Svetlana V. Eliseeva,^{*,‡} Elvin V. Salerno,[‡] Beatriz A. Lopez Bermudez, Stéphane Petoud,^{*} and Vincent L. Pecoraro^{*}

ABSTRACT: Single lanthanide(III) ion white light emission is in high demand since it provides the advantage of requiring only one chromophore for the control of the color. Herein, a series of Ga³⁺/Dy³⁺ metallacrowns (MCs) is presented, demonstrating outstanding white light colorimetric properties with CIE chromaticity coordinates of (0.309, 0.334) and correlated color temperature (CCT) equal to 6670 K for the MC emitting the closest to the standard white color. Experimental data reveal that the CIE coordinates within the studied series of MCs are controlled mainly by the Dy³⁺-centered emission rather than by the ligand-centered bands, implying that Dy³⁺ can be tuned as a single ionic white light emitter by a simple modification of the coordination environment.

Controlled light is extremely important in the modern technological age. Systems which last longer, are brighter, and use less power are necessary to keep up with the increasing energy demand and to reduce environmental strain. White light emission (WLE) has a key role to play in general lighting, displays, and communications (e.g. emerging “LiFi” technology).¹ For general lighting, pure white light is desirable such that our color perception is true. Indeed, the quality and constancy of white light is essential for a broad range of applications, a typical example being surgical settings where it is critical that physicians can unambiguously perceive proper colors within their working environment.² Bright, constant and calibrated WLE is also of major importance for screen backlighting in LCD or LED displays.³ These types of flat displays function by modulating the component colors of the white light which pass through their filters.⁴ In CIE (Commission Internationale d’Eclairage) 1931 color coordinates, which are used to quantify a standardized human perception of color, (*x*, *y*) coordinates of (0.33, 0.33) are considered as providing an optimal white light emission.⁵

One way to categorize strategies of production of white light is based on the number of emitting center types. Thus, dichroic, trichroic and tetrachroic strategies can be distinguished that use a combination of blue/yellow, red/green/blue (RGB) and RGB/cyano emitters, respectively.⁶ Oftentimes, different co-doped lanthanide(III) ions (Ln³⁺) can produce these colored emissions. Ln³⁺ emission can also be combined with blue organic emissions.^{7,8} Ln³⁺ are attractive for this application as they emit “pure colors” as sharp emission bands, the wavelengths of which are not highly affected by changes in the experimental conditions (such as the temperature, for example). Alternatively, multiple materials with individual colorimetric characteristics can be combined in an appropriate ratio.¹ Single-compound emitters are highly desirable since they have the potential to be the main component for a simpler production of lighter and thinner materials.⁹ This approach has been used, for example, with the 1,8-naphthalimide/Eu³⁺ complex, in

which green and blue emissions from the chromophoric ligand have been coupled with Eu³⁺ red emission to form observed white light;¹⁰ or in a binuclear Dy³⁺ complex where blue ligand emission has been combined with complementary Dy³⁺ yellow emission.¹¹

The design of such complexes is often difficult since it is unlikely that one chromic component can be altered without affecting the others in an unpredictable manner. A different approach is based on the emission from a single ion as the resulting global emission is more easily tunable along one experimental coordinate. WLE derived from Dy³⁺ has been demonstrated in solid state glasses. For example, Kaewkhao *et al.* have found that WLE characteristics were different for bismuth borate and zinc bismuth borate glasses doped with similar concentrations of Dy³⁺.¹² Other studies involving Dy³⁺-doped barium silicate¹³ and lithium zinc borosilicate¹⁴ glasses have demonstrated that CIE coordinates could be tuned by the choice of Dy³⁺ doping concentration.

Herein, we present a series of single-molecular white light emitting Ga³⁺/Dy³⁺ metallacrowns (MCs) with optical excitation at 340 nm. We simultaneously present evidence that WLE characteristics of single Dy³⁺ ions can be modulated by altering the crystal field (CF) about them.

Each of the presented MCs shares a common 12-metallacrown-4 motif based on diamagnetic Ga³⁺ ring metals and salicylhydroxamic acid (H₃shi) ring ligands, [12-MC_{Ga}^{III}N_(shi)-4];^{15,16} however, the geometry about the Dy³⁺, as well as the counter cations balancing charges in the structures are varied. Four MCs that we have previously described are newly analyzed for WLE: [DyGa₄(shi)₄(bz)₄](pyH) (**1**),¹⁷ [DyGa₄(shi)₄(H₂shi)₂(NO₃)] (**2**),¹⁸ [Dy₂Ga₈(shi)₈(ip)₄](NH₄)₂ (**3**),¹⁹ [DyGa₈(shi)₈(OH)₄]Na (**4**)²⁰ (bz⁻ = benzoate, pyH⁺ = pyridinium, ip²⁻ = isophthalate). In addition, the novel MC, [DyGa₄(shi)₄(bz)₄]Na (**5**), has been synthesized and fully characterized (Figure 1, Scheme S1). **5** is an identical MC to **1**, with the difference of containing a sodium counter cation rather than a pyridinium cation. This substitution was made to evaluate if the reduction of the number of C-H and N-H

oscillators in the solid state could increase the Dy³⁺-centered quantum yield (Q_{Dy}^L) of the Ga³⁺/Dy³⁺ MC since X-H oscillators are known to non-radiatively deactivate the excited states of Ln³⁺.²¹

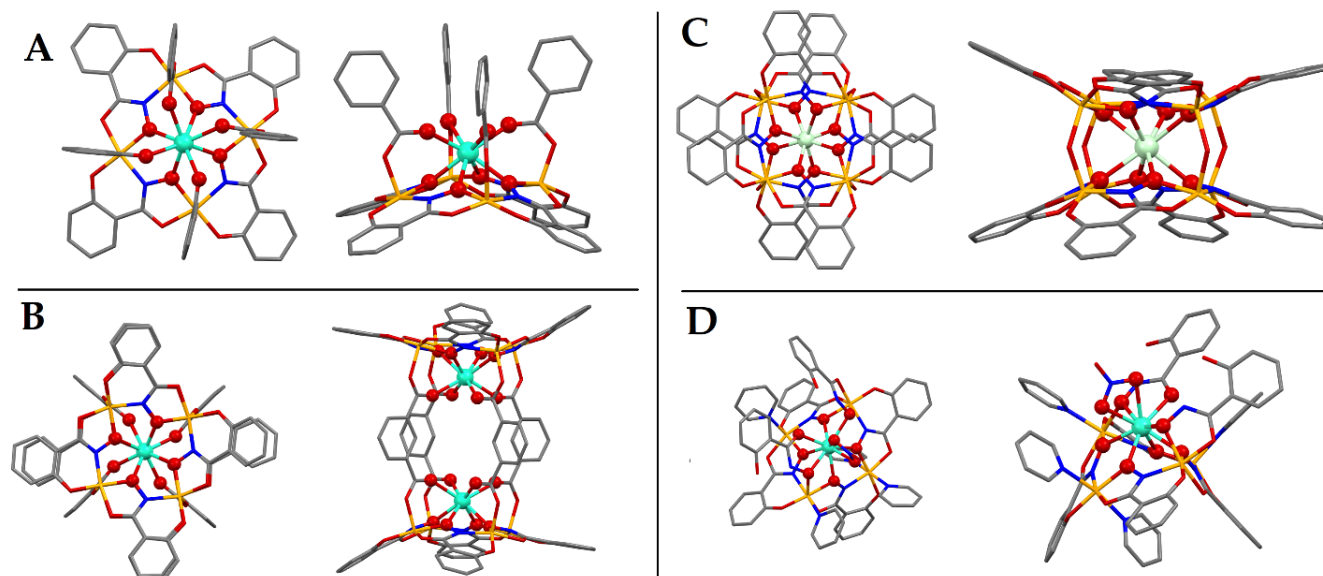


Figure 1. Multiple views of the Ga³⁺/Dy³⁺ MCs geometries. (A) [DyGa₄(shi)₄(bz)₄] corresponding to **1** and **5**. The crystal structure was solved for [DyGa₄(shi)₄(bz)₄(pyH)] (**1**),¹⁷ however mass spectrometry and elemental analysis reveal identical molecular composition (Supporting Information). (B) [Dy₂Ga₈(shi)₈(ip)₄(NH₄)₂] (**3**).¹⁹ (C) [DyGa₈(shi)₈(OH)₄]Na (**4**).²⁰ The structure was solved for isostructural [NdGa₈(shi)₈(OH)₄]Na. (D) [DyGa₄(shi)₄(H₂shi)₂(NO₃)] (**2**).¹⁸ The structure was solved for isostructural [TbGa₄(shi)₄(H₂shi)₂(NO₃)], four coordinating pyridines are shown here. Solvents of crystallization, non-integral counter ions, and hydrogen atoms are omitted. Central Ln³⁺ and coordinating oxygen atoms are bolded for highlight effect. Color code: Ga-orange; Na-violet; Ln-teal; O-red; N-blue; C-grey.

Excitation spectra of Ga³⁺/Dy³⁺ MCs upon monitoring the ⁴F_{9/2}→⁶H_{13/2} transition appearing at 575–577 nm are dominated by the broad bands in the UV up to 400 nm with sharp features of lower intensity that correspond to the Dy³⁺ f-f transitions (Figure S2). Such behavior confirms an efficient sensitization of Dy³⁺ emission through the MC scaffold. Within the studied series of Ga³⁺/Dy³⁺ MCs, the energy positions of the ligand triplet states (T₁) are similar (Table S2). This observation can be explained by the major role of the [12-MC_{Ga}^{III}_N(shi)-4] moieties in the sensitization of Dy³⁺ emission in all MCs, rather than the other residues found in the complexes, i.e. bz⁻, ip²⁻, pyH⁺, and OH⁻. The nature of the latter, however, are highly relevant to changes of the CF about the Dy³⁺.

To analyze WLE properties, Ga³⁺/Dy³⁺ MCs were optically excited at 340 nm and emission spectra were recorded in the range of 360–700 nm (Figure 2) and used for the calculation of the corresponding CIE coordinates and CCT (Correlated Color Temperature) values (Figure 3, Tables 1 and S4). CCT defines the color appearance of a white light. Warm light is around 2700 K, neutral white is around 4000 K, and cool white is >5000 K. Emission spectra of Ga³⁺/Dy³⁺ MCs have a generally similar emission profile: (i) a weak and broad band in the range of 360–445 nm corresponding to π-π* transitions within the organic ligands, and (ii) three sharp bands in the range of 445–700 nm that are assigned to Dy³⁺ ⁴F_{9/2}→⁶H_{*J*} (*J* = 15/2, 13/2, 11/2) transitions. However, the relative intensities of these emission bands (Table S3) as well crystal-field splitting of the f-f transitions vary depending on the composition of the MC. The latter also affects quantitative characteristics of **1**–**5**, namely ligand-centered (Q_L^L) and Q_{Dy}^L quantum

yields (Table 1) as well as Dy³⁺ luminescence lifetimes (τ_{obs} , Table S5). It should be noted that despite the similarity of the T₁ energies of the ligands within the series of Ga³⁺/Dy³⁺ MCs, Q_{Dy}^L and τ_{obs} vary significantly- from 0.222(6) to 8.3(3)% and 3.36(6) to 50.9(6) μs, respectively. An important consideration is the role of the counter-cation already mentioned by us for [Yb₂Ga₈(shi)₈(ip)₄] dimers.²² Indeed, the τ_{obs} is 2.4 times longer for **5** compared to **1** (50.9(6) vs. 21.2(2) μs), while Q_{Dy}^L is enhanced 6.3-times reaching 8.3(3)% for the former MC.

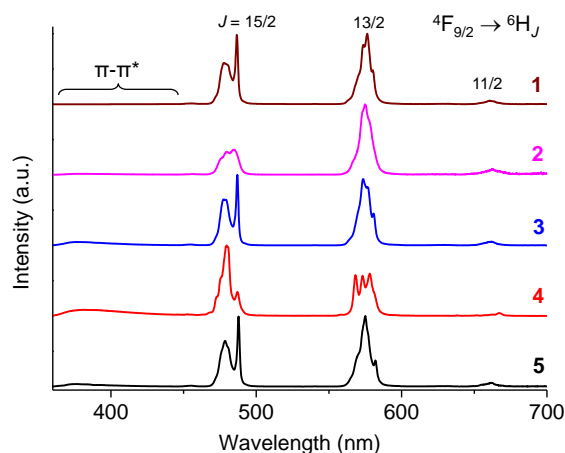


Figure 2. Corrected and normalized emission spectra of Ga³⁺/Dy³⁺ MCs in the solid state under excitation at 340 nm, room temp.

Considering the resulting CIE diagram, three main groups could be distinguished as corresponding to the three general molecular geometries (Table S1, Figures 1 and S1). Compounds **1**, **3**, and **5** have all similar 8-coordinate pseudo- C_4 symmetry. Indeed, **1** and **5** are identical molecular units with disparate counter cations, while **3** is the structural dimer of **1** and **5** where the bz ligands bridging Dy^{3+} to the [12-MC $_{Ga^{III}N(shi)}-4$] core have been replaced with ip $^{2-}$ to link the two DyGa $_4$ monomers. These structures possess four oxygen atoms derived from the shi $^{3-}$ ligands, and four oxygen atoms derived from the aromatic carboxylates, either bz (1, 5) or ip $^{2-}$ (3). MC **2** is a less symmetrical 9-coordinate complex with a symmetry more akin to a simple C_1 . It has four oxygen atoms derived from the shi $^{3-}$, as well as two oxygen atoms from the nitrate anion bound in a μ_2 -NO $_3$ pattern, and finally, three oxygen atoms from the H $_2$ shi $^{3-}$ bridging ligands. **4** is the most symmetrical MC within the series exhibiting pseudo- S_8 symmetry with eight oxygen atoms from the shi $^{3-}$ coordinating in an approximately square antiprismatic geometry. Because all coordinating atoms in **4** are coming from the MC core, the two [12-MC $_{Ga^{III}N(shi)}-4$] planes are essentially equidistant from Dy^{3+} in this molecule. It should be noted that MCs **1**, **3**, **4** and **5** have essentially a planar [12-MC $_{Ga^{III}N(shi)}-4$] core, while **2** possesses a highly distorted MC ring.

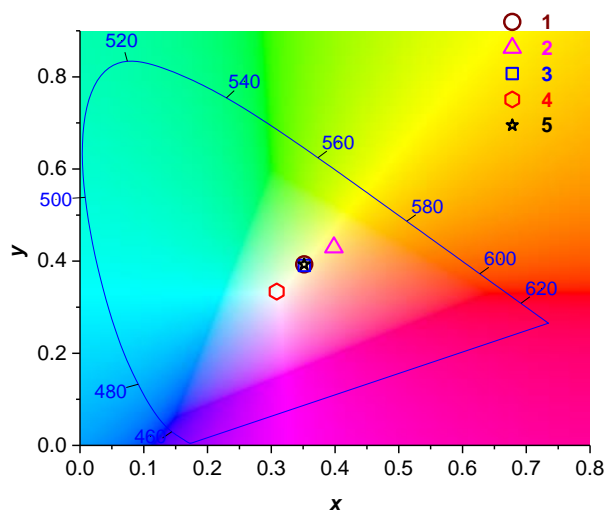


Figure 3. CIE 1931 chromaticity coordinate diagram for **1-5**.

Table 1. Quantum yields and CIE 1931 coordinates (x , y) for Ga^{3+}/Dy^{3+} MCs in the solid state.

MC	x^b	y^b	CCT (K) ^c	$Q_{Dy}^L(\%)^d$	$Q_L^L(\%)^e$	$\frac{Q_L^L}{Q_{Total}^L}$
1	0.352	0.393	4888	1.23(2)	0.0043(1)	0.0035
2	0.398	0.430	3917	0.222(6)	0.0091(1)	0.039
3	0.352	0.391	4882	0.85(1)	0.086(1)	0.092
4	0.309	0.334	6670	1.42(8)	0.34(1)	0.193
5	0.352	0.393	4888	8.3(3)	0.54(2)	0.060

^aAt room temperature upon 330-350 nm excitation; 2σ values between parentheses; experimental errors: Q , $\pm 10\%$. ^bCalculated for the 380-700 nm range. ^cEstimated from CIE coordinates using eq. (S1a,b). ^dThe quantum yield of the Dy^{3+} -centered emission. ^eThe quantum yield of the ligand-centered emission.

The nature of the ligands is not only important in controlling the luminescence properties of the Dy^{3+} -centered emission, the ligand-centered emission may also contribute to the overall luminescence profile (Figure 2) of the MC and, in turn, affect CIE coordinates. Analysis of the corresponding quantum yields allowed to estimate the magnitude of the ligands contribution to the total emission (Table 1). This parameter varies from 0.35% for **1** to 19.3% for **4**. For the C_4 -type MCs (**1**, **3** and **5**), the similar CIE coordinates and CCT values were found regardless the contribution of the ligands emission and the quantum yield values. The nature of the counter-cation (essential for Q_{Dy}^L and τ_{obs}) has a minimal effect on the color characteristics (**1** vs. **5**). On the other hand, **2** emits a much warmer light than **4** (Figure 3). Nevertheless, the contribution of the ligand emission to CIE coordinates of Ga^{3+}/Dy^{3+} MCs can be considered as being minimal compared to the impact of the CF induced by the coordination environment about Dy^{3+} (Table S4, Figure S3).

Taking the latter point into account, it appears that Dy^{3+} WLE can be tuned solely on the basis of the CF that is able to change the Stark splitting and the intensity of each of the Dy^{3+} electronic transitions.²³⁻²⁵ The Dy^{3+} emission signals in the visible region arise from the $^4F_{9/2}$ emitting state (Figure 2). Since human perception of white light is dependent on the additive contributions from multiple visible colors, the wavelength and relative intensities of these transitions are highly important. The contributing transitions in the visible region for Dy^{3+} are $^4F_{9/2} \rightarrow ^6H_{15/2}$ (480 nm, blue), $^4F_{9/2} \rightarrow ^6H_{13/2}$ (575 nm, golden-yellow), and minimally $^4F_{9/2} \rightarrow ^6H_{11/2}$ (665 nm, red). The human colorimetric perception of the corresponding wavelengths was assigned based on Helmholtz's color assessment.²⁶ By this scheme, the Dy^{3+} ion is a tri-chroic white light producer possessing particular relative integrated intensities of each blue, golden-yellow, and red contributions (Table S3). As a consequence, CIE coordinates can be tuned by the CF. Indeed, **1**, **3** and **5** with pseudo- C_4 symmetry exhibit emission bands with similar Stark splitting and relative integrated intensities for blue (39-44%), golden-yellow (48-52%) and red (3.6-4.0%) contributions. The emission spectrum of the less symmetrical **2** is dominated by the $^4F_{9/2} \rightarrow ^6H_{13/2}$ transition (60%) while blue and red components contribute at levels of 28 and 8.2%, respectively, moving its CIE coordinates and CCT to the warm white region. Finally, **4** displays the closest CIE coordinates to standard white light and exhibits an emission spectrum with similar contributions from blue and golden-yellow components (42 and 36%), in addition to the 2% red contribution.

In summary, a series of five Ga^{3+}/Dy^{3+} MCs were analyzed for their WLE properties, with the novel [DyGa $_4$ (shi) $_4$ (bz) $_4$]Na (**5**) demonstrating the ability to drastically increase the Q_{Dy}^L by the judicious selection of the molecular counter cation. Moreover, CIE coordinates of [DyGa $_8$ (shi) $_8$ (OH) $_4$]Na (**4**) (0.309, 0.334) are close to the ideal white light with CCT in the cold white region. Importantly, the present study represents a promising approach for the tuning of single Dy^{3+} WLE based on CF considerations and is likely to be transferrable across different Dy^{3+} host compounds.

ASSOCIATED CONTENT

Experimental details and additional information about analysis of crystal structures and photophysical data. This material is available free of charge via the Internet at <http://pubs.acs.org>.

AUTHOR INFORMATION

*Corresponding Authors

Svetlana V. Eliseeva - *Centre de Biophysique Moléculaire, CNRS UPR 4301, F-45071 Orleans Cedex 2, France.*
Email: svetlana.eliseeva@cnrs-orleans.fr

Stéphane Petoud - *Centre de Biophysique Moléculaire, CNRS UPR 4301, F-45071 Orleans Cedex 2, France.*
Email: stephane.petoud@inserm.fr

Vincent L. Pecoraro - *Department of Chemistry, Willard H. Dow Laboratories, University of Michigan, Ann Arbor, Michigan 48109, USA;*
Email: vlpec@umich.edu

Authors

Elvin V. Salerno - *Department of Chemistry, Willard H. Dow Laboratories, University of Michigan, Ann Arbor, Michigan 48109, USA.*

Beatriz A. Lopez Bermudez - *Department of Chemistry, Willard H. Dow Laboratories, University of Michigan, Ann Arbor, Michigan 48109, USA.*

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript. ‡These authors contributed equally.

ACKNOWLEDGMENTS

The work was supported through grants from the National Science Foundation (CHE 1664964 for VLP and EVS, DGE-1256260 for EVS), La Ligue Contre le Cancer and La Région Centre Val de Loire. SP thanks Institut National de la Santé et de la Recherche Médicale.

ABBREVIATIONS

CCT, Correlated Color Temperature; CF, crystal field; CIE, Commission Internationale d'Eclairage; LCD, liquid crystal display; LED, light-emitting diode; MC, metallacrown; WLE, white light emission.

REFERENCES

- (1) Cho, J.; Park, J. H.; Kim, J. K.; Schubert, E. F. White Light-Emitting Diodes: History, Progress, and Future. *Laser Photonics Rev.* **2017**, *11* (2); 1600147. <https://doi.org/10.1002/lpor.201600147>.
- (2) Knulst, A. J.; Stassen, L. P. S.; Grimbergen, C. A.; Dankelman, J. Choosing Surgical Lighting in the LED Era. *Surg. Innov.* **2009**, *16* (4) e44048, 317–323. <https://doi.org/10.1177/1553350609353766>.
- (3) Chen, H.-W.; Lee, J.-H.; Lin, B.-Y.; Chen, S.; Wu, S.-T. Liquid Crystal Display and Organic Light-Emitting Diode Display: Present Status and Future Perspectives. *Light Sci. Appl.* **2018**, *7* (3), 17168–17168. <https://doi.org/10.1038/lsa.2017.168>.
- (4) Elze, T.; Tanner, T. G. Temporal Properties of Liquid Crystal Displays: Implications for Vision Science Experiments. *PLoS One* **2012**, *7* (9). <https://doi.org/10.1371/journal.pone.0044048>.
- (5) Choudhury, A. K. R. Using Instruments to Quantify Colour. In *Principles of Colour and Appearance Measurement*; Woodhead Publishing, 2014; pp 270–317. <https://doi.org/10.1533/9780857099242.270>.
- (6) SeethaLekshmi, S.; Ramya, A. R.; Reddy, M. L. P.; Varughese, S. Lanthanide Complex-Derived White-Light Emitting Solids: A Survey on Design Strategies. *J. Photochem. Photobiol. C Photochem. Rev.* **2017**, *33*, 109–131. <https://doi.org/10.1016/j.jphotochemrev.2017.11.001>.
- (7) Yang, Q. Y.; Wu, K.; Jiang, J. J.; Hsu, C. W.; Pan, M.; Lehn, J. M.; Su, C. Y. Pure White-Light and Yellow-to-Blue Emission Tuning in Single Crystals of Dy(III) Metal–Organic Frameworks. *Chem. Commun.* **2014**, *50* (57), 7702–7704. <https://doi.org/10.1039/c4cc01763c>.
- (8) Kotova, O.; Comby, S.; Lincheneau, C.; Gunnlaugsson, T. White-Light Emission from Discrete Heterometallic Lanthanide-Directed Self-Assembled Complexes in Solution. *Chem. Sci.* **2017**, *8* (5), 3419–3426. <https://doi.org/10.1039/c7sc00739f>.
- (9) Law, G. L.; Wong, K. L.; Tam, H. L.; Cheah, K. W.; Wong, W. T. White OLED with a Single-Component Europium Complex. *Inorg. Chem.* **2009**, *48* (22), 10492–10494. <https://doi.org/10.1021/ic9018037>.
- (10) Shelton, A. H.; Sazanovich, I. V.; Weinstein, J. A.; Ward, M. D. Controllable Three-Component Luminescence from a 1,8-Naphthalimide/Eu(III) Complex: White Light Emission from a Single Molecule. *Chem. Commun.* **2012**, *48* (22), 2749–2751. <https://doi.org/10.1039/c2cc17182a>.
- (11) Manzur, J.; De Santana, R. C.; Maia, L. J. Q.; Vega, A.; Spodine, E. Tuning White Light Emission in Dinuclear Phenoxo Bridged Dy^{III} Complexes. *Inorg. Chem.* **2019**, *58* (15), 10012–10018. <https://doi.org/10.1021/acs.inorgchem.9b01153>.
- (12) Yasaka, P.; Boonin, K.; Kaewkhao, J. White Light Emission from Dy³⁺ Doped Zinc Bismuth Borate and Bismuth Borate Glasses: A Comparative Study. *Key Eng. Mater.* **2016**, *675–676*, 409–413. <https://doi.org/10.4028/www.scientific.net/KEM.675-676.409>.
- (13) Mishra, L.; Sharma, A.; Vishwakarma, A. K.; Jha, K.; Jayasimhadri, M.; Ratnam, B. V.; Jang, K.; Rao, A. S.; Sinha, R. K. White Light Emission and Color Tunability of Dysprosium Doped Barium Silicate Glasses. *J. Lumin.* **2016**, *169*, 121–127. <https://doi.org/10.1016/j.jlumin.2015.08.063>.
- (14) Jaidass, N.; Krishna Moorthi, C.; Mohan Babu, A.; Reddi Babu, M. Luminescence Properties of Dy³⁺ Doped Lithium Zinc Borosilicate Glasses for Photonic Applications. *Heliyon* **2018**, *4* (3), e00555. <https://doi.org/10.1016/j.heliyon.2018.e00555>.
- (15) Lutter, J. C.; Zaleski, C. M.; Pecoraro, V. L. Chapter Four - Metallacrowns: Supramolecular Constructs With Potential in Extended Solids, Solution-State Dynamics, Molecular Magnetism, and Imaging. In *Advances in Inorganic Chemistry*; van Eldik, R., Puchta, R. B. T.-A. in I. C., Eds.; Academic Press, 2018; Vol. 71, pp 177–246. <https://doi.org/https://doi.org/10.1016/bs.adioch.2017.11.007>.
- (16) Mezei, G.; Zaleski, C. M.; Pecoraro, V. L. Structural and Functional Evolutions of Metallacrowns. *Chem. Rev.* **2007**, *107* (11), 4933–5003. <https://doi.org/10.1021/cr078200h>.
- (17) Chow, C. Y.; Eliseeva, S. V.; Trivedi, E. R.; Nguyen, T. N.; Kampf, J. W.; Petoud, S.; Pecoraro, V. L. Ga³⁺/Ln³⁺ Metallacrowns: A Promising Family of Highly Luminescent Lanthanide Complexes That Covers Visible and Near-Infrared Domains. *J. Am. Chem. Soc.* **2016**, *138* (15), 5100–5109. <https://doi.org/10.1021/jacs.6b00984>.
- (18) Nguyen, T. N.; Eliseeva, S. V.; Chow, C. Y.; Kampf, J. W.; Petoud, S.; Pecoraro, V. L. Peculiarities of Crystal Structures and Photophysical Properties of Ga³⁺/Ln³⁺ Metallacrowns with a Non-Planar [12-MC-4] Core. *Inorg. Chem. Front.* **2020**, *7*, 1553–1563. <https://doi.org/10.1039/c9qi01647c>.
- (19) Nguyen, T. N.; Chow, C. Y.; Eliseeva, S. V.; Trivedi, E. R.; Kampf, J. W.; Martinić, I.; Petoud, S.; Pecoraro, V. L. One-Step Assembly of Visible and Near-Infrared Emitting Metallacrown Dimers Using a Bifunctional Linker. *Chem. - A Eur. J.* **2018**, *24* (5), 1031–1035. <https://doi.org/10.1002/chem.201703911>.
- (20) Salerno, E. V.; Eliseeva, S. V.; Schneider, B. L.; Kampf, J. W.; Petoud, S.; Pecoraro, V. L. Visible, near-Infrared, and Dual-Range Luminescence Spanning the 4f Series Sensitized by Dimeric Gallium(III)/Lanthanide(III) Metallacrown. *Submitted*.
- (21) Bünzli, J.-C.; Eliseeva, S. V. Basics of Lanthanide Photophysics. In *Lanthanide Luminescence: Photophysical, Analytical and Biological Aspects*; Springer-Verlag Berlin Heidelberg, 2011; pp 1–46. <https://doi.org/10.1007/978-3-642-21023-5>.
- (22) Lutter, J. C.; Eliseeva, S. V.; Collet, G.; Martinić, I.; Kampf, J. W.; Schneider, B. L.; Carichner, A.; Sobilo, J.; Lerondel, S.; Petoud, S.; Pecoraro, V. L. Iodinated Metallacrowns: Toward Combined Bimodal Near-Infrared and X-ray Contrast Imaging Agents. *Chem. - A Eur. J.* **2019**, *26*, 1274–1277. <https://doi.org/10.1002/chem.201905241>.
- (23) Walsh, B. M. Judd-Ofelt Theory: Principles and Practices. In *Advances in Spectroscopy for Lasers and Sensing*; Springer, Dordrecht, 2006; pp 403–433. https://doi.org/https://doi.org/10.1007/1-4020-4789-4_21.
- (24) Schweizer, T.; Hewak, D. W.; Samson, B. N.; Payne, D. N. Spectroscopic Data of the 1.8-, 2.9-, and 4.3- μm Transitions in Dysprosium-Doped Gallium Lanthanum Sulfide Glass. *Opt. Lett.* **1996**, *21* (19), 1594–1596.

- (25) Sastri, V. S.; Bünzli, J.-C.; Rao, V. R.; Rayudu, G. V. S.; Perumareddi, J. R. Spectroscopy of Lanthanide Complexes. In *Modern Aspects of Rare Earths and Their Complexes*; 2003; pp 569–731. <https://doi.org/10.1016/b978-044451010-5/50022-5>.
- (26) Choudhury, A. K. R. Principles of Colour Perception. In *Principles of*

Colour and Appearance Measurement; Woodhead Publishing, 2014; pp 144–184. <https://doi.org/10.1533/9780857099242.144>.

