



**HAL**  
open science

## Sequential Spin State Transition and Intermetallic Charge Transfer in $\text{PbCoO}_3$

Xubin Ye, Shijun Qin, Angel Arévalo-López, Changqing Jin, Zhehong Liu, Yuki Sakai, Junye Yang, Wenmin Li, Ying Liu, Jinming Chen, et al.

► **To cite this version:**

Xubin Ye, Shijun Qin, Angel Arévalo-López, Changqing Jin, Zhehong Liu, et al.. Sequential Spin State Transition and Intermetallic Charge Transfer in  $\text{PbCoO}_3$ . *Journal of the American Chemical Society*, 2020, 142 (12), pp.5731-5741. 10.1021/jacs.9b13508 . hal-03085811

**HAL Id: hal-03085811**

**<https://hal.science/hal-03085811>**

Submitted on 17 Jul 2021

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Sequential Spin State Transition and Intermetallic Charge Transfer in PbCoO<sub>3</sub>

Zhehong Liu<sup>⊥, //</sup>, Yuki Sakai<sup>§, ▲</sup>, Junye Yang<sup>⊥</sup>, Wenmin Li<sup>⊥, //</sup>, Ying Liu<sup>⊥, //</sup>, Xubin Ye<sup>⊥, //</sup>, Shijun Qin<sup>⊥, //</sup>, Jinming Chen<sup>\*, ○</sup>, Stefano Agrestini<sup>∞</sup>, Kai Chen<sup>∞</sup>, Sheng-Chieh Liao<sup>∞</sup>, Shu-Chih Haw<sup>○</sup>, Francois Baudalet<sup>◇</sup>, Hirofumi Ishii<sup>○</sup>, Takumi Nishikubo<sup>▲</sup>, Hayato Ishizaki<sup>▲</sup>, Tatsuru Yamamoto<sup>▲</sup>, Zhao Pan<sup>▲</sup>, Masayuki Fukuda<sup>▲</sup>, Kotaro Ohashi<sup>▲</sup>, Kana Matsuno<sup>▲</sup>, Akihiko Machida<sup>◆</sup>, Tetsu Watanuki<sup>◆</sup>, Saori I. Kawaguchi,<sup>⊕</sup> Angel M. Arevalo-Lopez<sup>●, #</sup>, Changqing Jin<sup>⊥, //</sup>, Zhiwei Hu<sup>∞</sup>, J. Paul Attfield<sup>●</sup>, Masaki Azuma<sup>\*, ▲</sup>,  
§ & Youwen Long<sup>\*, ⊥, //, ⊕</sup>

<sup>⊥</sup>Beijing National Laboratory for Condensed Matter Physics, Institute of Physics, Chinese Academy of Sciences, Beijing 100190, China

<sup>//</sup>School of Physics, University of Chinese Academy of Sciences, Beijing 100049, China

<sup>§</sup>Kanagawa Institute of Industrial Science and Technology, 705-1 Shimoimaizumi, Ebina 243-0435, Japan

<sup>▲</sup>Laboratory for Materials and Structures, Tokyo Institute of Technology, 4259 Nagatsuta, Midori, Yokohama 226-8503, Japan

<sup>○</sup>National Synchrotron Radiation Research Center, 101 Hsin-Ann Road, Hsinchu 30076, Taiwan, R.O.C

<sup>∞</sup>Max-Planck Institute for Chemical Physics of Solids, Nöthnitzer Straße 40, 01187 Dresden, Germany

<sup>◇</sup>Synchrotron SOLEIL, L'Orme des Merisiers, Saint-Aubin-BP48, 91192 GIF-sur-YVETTE CEDEX, France

<sup>◆</sup>Quantum Beam Science Research Directorate, National Institutes for Quantum and Radiological Science and Technology, Sayo, Hyogo 679-5148, Japan

•Centre for Science at Extreme Conditions and School of Chemistry, University of Edinburgh, Mayfield Road, Edinburgh EH9 3JZ, United Kingdom

⊕ Japan Synchrotron Radiation Research Institute, SPring-8, 1-1-1 Kouto, Sayo, Hyogo 679-5198, Japan

⊕ Songshan Lake Materials Laboratory, Dongguan, Guangdong 523808, China

## ABSTRACT

Spin state transition and intermetallic charge transfer can essentially change material structural and physical properties with a fashion of excluding external chemical doping. However, these two effects have **rarely** been found to occur sequentially in a specific material. In this article, we show the realization of these two phenomena in **a perovskite oxide**  $\text{PbCoO}_3$  **with a simple  $\text{ABO}_3$  composition** under high pressure.  $\text{PbCoO}_3$  possesses a peculiar A- and B-site ordered charge distribution  $\text{Pb}^{2+}\text{Pb}^{4+}_3\text{Co}^{2+}_2\text{Co}^{3+}_2\text{O}_{12}$  with insulating behavior at ambient conditions. The high spin  $\text{Co}^{2+}$  gradually changes to low spin with increasing pressure up to about 15 GPa, leading to the anomalous increase of resistance magnitude. Between 15 GPa and 30 GPa, the intermetallic charge transfer occurs between  $\text{Pb}^{4+}$  and  $\text{Co}^{2+}$  cations. The accumulated charge-transfer effect triggers a metal-insulator transition as well as a first-order structural phase transition toward a Tetra.-I phase at the onset of  $\sim 20$  GPa near room temperature. On further compression over 30 GPa, the charge transfer completes, giving rise to another first-order structural transformation toward a Tetra.-II phase and the reentrant electrical insulating behavior.

## 1. INTRODUCTION

Transition-metal oxides exhibit a wide variety of intriguing physical properties and versatile functionalities such as ferroelectricity, ferromagnetism, catalysis,

superconductivity, colossal magnetoresistance, and magnetoelectric multiferroicity *etc* [1-9]. All these properties are closely related to the *d*-electron configurations of transition metals which involve the number of unpaired *d*-electrons as well as the detailed electronic distributions at different orbitals. Chemical substitution is a widely used method to modify the electronic configurations and thereby manipulate materials structures and properties. However, the external element doping may inevitably cause some inhomogeneous chemical disorders, which are unfavorable to understanding the intrinsic physical properties. On the other hand, there exist some “internal” effects that can also change the electronic configurations without the introduction of any doping element. A spin state transition is a typical example of one of these effects. As is well known, on heating the spin state of  $\text{Co}^{3+}$  in  $\text{LaCoO}_3$  gradually changes from low spin (LS) to high spin (HS) via a possible intermediate spin (IS) state, accompanied by magnetic and electrical transport variations [10-17]. Some other compounds containing Mn, Fe, and Co also show spin state transitions by changing the environment conditions such as temperature, pressure, and/or light radiation *etc* [18-26].

Intermetallic charge transfer is a more interesting manner to change the electronic configurations without introducing external element. In sharp contrast to spin state transitions, which only change the electronic states for a single cation, intermetallic charge transfer takes place between two different metals, so that much more drastic variations in structure, magnetism, and electrical transport properties are expected to jointly occur. Compared with a spin state transition, intermetallic charge transfer is only observed in a few transition-metal oxides. An interesting example is  $\text{LaCu}_3\text{Fe}_4\text{O}_{12}$ , where Cu-Fe intermetallic charge transfer occurs on heating to 393 K or pressuring to 3.6 GPa at room temperature (RT), resulting in the change of charge combination from  $\text{LaCu}^{3+}_3\text{Fe}^{3+}_4\text{O}_{12}$  to  $\text{LaCu}^{2+}_3\text{Fe}^{3.75+}_4\text{O}_{12}$  accompanying with insulator-to-metal and antiferromagnetism-to-paramagnetism transformations as well as the presence of negative thermal expansion [27,28]. Similarly, intermetallic charge

transfer is also observed in BiNiO<sub>3</sub> between Bi and Ni, causing the charge format change from Bi<sup>3+</sup><sub>0.5</sub>Bi<sup>5+</sup><sub>0.5</sub>Ni<sup>2+</sup>O<sub>3</sub> to Bi<sup>3+</sup>Ni<sup>3+</sup>O<sub>3</sub> [29].

Although spin state transition and intermetallic charge transfer have received much attention in the past, these two phenomena are **rare** to occur together in a specific material. **The only report is in a perovskite oxide family with a complicated composition, (Pr<sub>1-x</sub>R<sub>x</sub>)<sub>0.7</sub>Ca<sub>0.3</sub>CoO<sub>3</sub> (R=Y, Sm) composed of mixed Co<sup>3+</sup>/Co<sup>4+</sup> and Pr<sup>3+</sup>/Pr<sup>4+</sup> states [30-36].** The high-pressure synthesized **perovskite oxide** PbCoO<sub>3</sub> provides a unique opportunity for **such a discovery in a compound with a simple ABO<sub>3</sub> composition.** On account of the peculiar A- and B-site charge orderings, PbCoO<sub>3</sub> crystallizes in an AA'<sub>3</sub>B<sub>2</sub>B'<sub>2</sub>O<sub>12</sub>-type quadruple perovskite structure (Fig. 1) with the charge combination of Pb<sup>2+</sup>Pb<sup>4+</sup><sub>3</sub>Co<sup>2+</sup><sub>2</sub>Co<sup>3+</sup><sub>2</sub>O<sub>12</sub>, where the Co<sup>2+</sup> is confirmed to be HS with the spin value  $S = 3/2$  while Co<sup>3+</sup> is LS with  $S = 0$  [37]. The former has a magnetic frustration owing to the tetrahedral arrangement and orders antiferromagnetically below 7.8 K. HS Co<sup>2+</sup> is sensitive to external stimuli like high pressure, at which a HS-to-LS transition is highly likely to occur, as observed in CoO and other Co<sup>2+</sup>(HS)-containing compounds [18,38]. In addition, the 6s states of Pb have similar energy levels with those of the *d* orbitals of Co [37]. As a result, moderate stimuli may also trigger the Pb-Co intermetallic charge transfer, causing different charge combination and physical properties [37, 39]. In this paper, we report the realization of both spin state transition and intermetallic charge transfer accompanying with double metal-insulator and crystal structure phase transitions in PbCoO<sub>3</sub> as evidenced by a series of *in situ* high-pressure measurements including electrical transport, neutron diffraction, synchrotron X-ray diffraction, emission, and absorption spectroscopies.

## 2. METHODS SECTION

Polycrystalline PbCoO<sub>3</sub> samples were prepared at high pressure and high temperature

conditions as reported before [37]. High purity (>99.9%) PbO, PbO<sub>2</sub> and Co<sub>3</sub>O<sub>4</sub> starting materials with a mole ratio of 1:2:1 were well mixed in an agate mortar. The mixed powders were then pressed into a gold capsule with 3 mm in diameter and length for further treatment at 12 GPa and 1323 K for 30 min using a Walker-type multianvil high pressure apparatus. When the heating time was finished, the sample was quenched to room temperature, and then the pressure was slowly released to ambient pressure. X-ray powder diffraction was performed to identify the sample quality using a Huber diffractometer (Cu K $\alpha$ <sub>1</sub> radiation, 40 kV, 30 mA).

The electronic transport properties of PbCoO<sub>3</sub> at high pressure were measured using the standard four-probe method with a screw type diamond anvil cell (DAC) made of nonmagnetic Be-Cu alloy as described elsewhere [40]. The diamond culet was 300  $\mu$ m in diameter and a T301 stainless steel gasket was pre-indented from 250  $\mu$ m to 40  $\mu$ m thickness with a center hole of 150  $\mu$ m in diameter. The gasket was then covered by cubic BN fine powders to be the insulating layer which drilled with a diameter of 80  $\mu$ m hole served as sample chamber. The PbCoO<sub>3</sub> fine powders pressed with a dimension of 50 $\times$ 50 $\times$ 10  $\mu$ m<sup>3</sup> was loaded with soft NaCl fine powder surrounding as pressure transmitting medium. We used slim Au wire of 18  $\mu$ m diameter as electrodes. Pressures were calibrated by ruby fluorescence shift method for all the DAC-related experiments used in this paper [41]. The DAC was placed inside a Mag-Lab system to perform the experiments. A thermometer located around the sample in the DAC was used for monitoring the sample temperature.

High-pressure synchrotron x-ray emission spectroscopy (XES) and absorption spectroscopy (XAS) were measured using DAC techniques at RT. The pressure dependent Co-K XAS spectra were measured at the ODE beamline of the synchrotron SOLEIL, France. The Co-metal foil was used as reference for the cobalt chemical shift. The high pressure Co K $\beta$  x-ray emission spectra with an overall resolution of  $\sim$ 0.9 eV and high resolution partial fluorescence yield Pb-L<sub>3</sub> XAS spectra measured at Pb L<sub>1</sub> emission line with an overall resolution of  $\sim$ 2.5 eV were obtained at the

Taiwan inelastic x-ray scattering BL12XU beamline at SPring-8 in Japan. The Co  $K_{\beta}$  x-ray emission and Pb  $L_{\alpha 1}$  emission signals were analyzed with a spectrometer (Johann type) equipped with a spherically bent Ge(444) crystal and Si(555) (radius 1 m), respectively, arranged on a horizontal plane in a Rowland-circle geometry. The strong x-ray absorption of Pb ion leads to relative large error bar in Co  $K_{\beta}$  x-ray emission spectra of  $\text{PbCoO}_3$  as compared with that of  $\text{SrCo}_{0.5}\text{Ru}_{0.5}\text{O}_3$  [42].

The high-pressure synchrotron x-ray diffraction (SXR) experiment was performed at beamline BL22XU in SPring-8 by using DACs with rhenium and stainless-steel gaskets. Helium was used as a pressure medium. The wavelengths of 0.4964 and 0.4961 Å were used in the room- and low-temperature experiments, respectively. The RIETAN-FP program was used to analyze the SXR data [43]. Time-of-flight neutron powder diffraction (NPD) data at high pressure and RT conditions were recorded with the instrument PEARL/HiPr at the ISIS facility, U.K. About 90 mm<sup>3</sup> of the sample was loaded into a Paris-Edinburgh cell [44] with 4:1 methanol-ethanol as a pressure medium and a small pellet of lead as the pressure calibrate. Rietveld profile refinements of the structural models were performed with the GSAS software [45].

### 3. RESULTS AND DISCUSSION

Fig. 1 shows the schematic crystal structure for the quadruple perovskite oxide  $\text{Pb}^{2+}\text{Pb}^{4+}_3\text{Co}^{2+}_2\text{Co}^{3+}_2\text{O}_{12}$  with space group  $Pn-3$  at ambient conditions. In this crystal symmetry, the  $\text{Pb}^{2+}$  and  $\text{Pb}^{4+}$  are 1:3 ordered at the A and A' sites, forming  $\text{Pb}^{2+}\text{O}_{12}$  and square-planar  $\text{Pb}^{4+}\text{O}_4$  coordinated units, respectively. In spite of the smaller charge difference, the large discrepancy of ionic radius between the HS  $\text{Co}^{2+}(t_{2g}^5e_g^2)$  and the LS  $\text{Co}^{3+}(t_{2g}^6e_g^0)$  makes them ordered at the octahedral coordinated B/B' sites with a rocksalt-type manner. This is similar with that observed in  $\text{La}_{1.5}\text{Sr}_{0.5}\text{CoO}_4$ , where the hopping of charge carriers between these two types of Co ions is confirmed

to be severely suppressed due to the spin-blockade effect [46].  $\text{PbCoO}_3$  thus also shows electrical insulating behavior at ambient pressure. For most  $3d$  transition-metal oxides, applying physical pressure can often enhance the  $p$ - $d$  hybridization and extend the  $d$ -electron bandwidth. As a consequence, the resistance under high pressure is expected to decrease. In sharp contrast, however, the resistance of  $\text{PbCoO}_3$  gradually increases as the pressure raises from 0.8 to 12.8 GPa, as shown in Fig. 2a. This unusual feature can be attributed to the continuous spin state transition of  $\text{Co}^{2+}$  from high spin to low spin, as will be further confirmed by synchrotron XES and NPD studies. Once the HS  $\text{Co}^{2+}$  to LS transition is complete, the electronic configuration will vary from  $t_{2g}^5 e_g^2$  to  $t_{2g}^6 e_g^1$ . In the  $\text{Co}^{2+}/\text{Co}^{3+}$ -site rocksalt-type ordered crystal structure, electron hopping between the low-spin  $\text{Co}^{2+}$  and  $\text{Co}^{3+}$  is also forbidden, or the ordered structure will be broken into a disordered one. Our SXRD reveals that the A- and B-site ordered  $Pn-3$  structure of  $\text{PbCoO}_3$  is unchanged up to  $\sim 20$  GPa near RT (shown later). Since the possible carrier hopping via the  $\text{Co}^{2+}$ -O-O- $\text{Co}^{2+}$  pathway should be significantly reduced when the HS-LS transition of  $\text{Co}^{2+}$  occurs, the resistance of  $\text{PbCoO}_3$  exhibits an unusual increase with pressure up to 12.8 GPa. Above 15.2 GPa, however, the magnitude of resistance starts to decrease. More strikingly, the temperature dependence of resistance changes in nature. One finds that the resistance sharply increases by several orders of magnitude as the temperature decreases from 270 K to 50 K at pressures below  $\sim 15$  GPa, whereas a weak temperature dependence with the change less than one order is found to occur once the pressure exceeds 15 GPa, although the insulating conductivity still shows up until to 18.4 GPa, as characterized by the raising resistance on cooling (Fig. 2a). These observations suggest that the spin state transition should complete around 15 GPa and other effects (such as Pb-Co charge transfer shown later) lead to the essential variation of resistivity in  $\text{PbCoO}_3$  above this pressure.

Under further compression to 21.0 and 27.1 GPa, metallic electrical transport behavior occurs at higher temperatures as shown in Fig. 2a and more clearly in Fig.

2b, indicating the melting of the ordered LS-Co<sup>2+</sup> and -Co<sup>3+</sup> states near RT. Moreover, lowering temperature changes the metallic state back to an insulating state, implying that the electronic states of Co<sup>2+</sup> and/or Co<sup>3+</sup> ions further change at lower temperatures. The critical temperature for the metal-insulator (MI) transition ( $T_{MI}$ ) at 21.0 GPa is about 214 K. In general, higher pressures will reduce the  $T_{MI}$  and eventually realize the metallization at a wider temperature region. Unexpectedly, however, the  $T_{MI}$  of PbCoO<sub>3</sub> shifts towards higher temperatures with further compression. For example, the value of  $T_{MI}$  increases to 244 K at 27.1 GPa. Furthermore, in the whole temperature range we measured, the MI transition disappears and only the electrical insulating behavior is observed from 32.2 GPa up to 48.9 GPa, the maximum pressure we applied for electrical transport measurement as presented in Fig. 2a. Therefore, if we plot the resistance values collected near RT as a function of pressure (Fig. 2c), one can distinguish several different electrical characteristic features. Below about 15 GPa, the compound shows insulating behavior, and the resistance linearly increases due to the HS-LS transition of Co<sup>2+</sup>. Above 15 GPa, there is an essential variation in electrical transport, and the resistance starts to decrease with pressure, indicating that a new mechanism rather than the spin state transition dominates the electrical transport, while the compound still maintains insulating behavior below ~20 GPa. Between 20 and 30 GPa, the MI transition appears, and the  $T_{MI}$  unusually shifts towards higher temperature with further compression. Above 30 GPa, the reentrant insulating behavior is found to occur in the whole temperature region we measured, and the values of resistance linearly decrease with pressure up to 48.9 GPa due to the normal physical pressure effect. Note that during the pressure release, the electrical transitions are all reversible (see Supplementary Fig. S1).

To further understand the series of interesting variations observed in electrical transport measurements, we performed pressure dependent XES and XAS measurements at RT for characterizing the spin states and valence states of Co and Pb.

Fig. 3 shows the Co- $K_{\beta}$  emission spectra of  $\text{PbCoO}_3$  measured at different pressures. At 0.5 GPa, the spectrum represents a main peak located at  $\sim 7,650$  eV corresponding to the  $K_{\beta_{1,3}}$  line, and a pronounced satellite peak at  $\sim 7,637$  eV corresponding to the  $K_{\beta'}$  line. The intensity ratio of the low-energy  $K_{\beta'}$  line to the main emission  $K_{\beta_{1,3}}$  line is proportional to the number of the unpaired electrons in the incomplete  $3d$  shell [47,48] and can be used to determine the spin state of Co ion as a function of temperature [17,49] and/or pressure [17,42,49-51]. With increasing pressure, the intensity of the low-energy  $K_{\beta'}$  line decreases and almost disappears above  $\sim 15$  GPa (Fig. 3), suggesting a decreasing spin moment of  $\text{Co}^{2+}$  ion. The inset of Fig. 3 contains a plot of the integrated absolute difference (IAD) as a function of pressure [17,42,49-51]. To get the IAD, all of the XES spectra were normalized with respect to the area under the curves and then shifted to have centers of mass at the same position. As an instance, the differential curve between 0.5 and 22.1 GPa is shown in Fig. 3. In this situation, the IAD value presents a linear relationship with the average spin number. In  $\text{PbCoO}_3$ , the total IAD changes by about 0.043(10) in going from 0.5 to 22.1 GPa. In comparison, for a complete HS- $\text{Co}^{3+}$  to LS- $\text{Co}^{3+}$  transition with spin change  $\Delta S = 2$ , the IAD value is 0.15 as observed in  $\text{Sr}_2\text{Co}_{0.5}\text{Ir}_{0.5}\text{O}_4$  [49]. In the present  $\text{PbCoO}_3$ , when the HS  $\text{Co}^{2+}$  changes into the LS one, the average  $\Delta S$  for the four Co ions per unit cell is 0.5, suggesting that the IAD value should be about 0.05. This value is comparable with the experimental observation, confirming the HS-LS transition of  $\text{Co}^{2+}$  in  $\text{PbCoO}_3$ . Since the IAD almost becomes naught with pressure going to about 15 GPa, we conclude that the spin state transition should complete around this pressure, in agreement with the electrical transport result. In addition, the continuous spin state transition was further supported by NPD under pressure as shown in Supplementary Table S1 and Fig. S2, where the observed shrinkage of  $\text{Co}^{2+}$ -O bond can be attributed to the HS to LS variation.

It is well known that the XAS at the transition metal  $K$  edge is very sensitive to the valence state of transition metal [52,53]. This technique is generally used to identify

the valence states of  $3d$  transition metals. Fig. 4a shows the Co- $K$  XAS spectra of  $\text{PbCoO}_3$  measured at different pressures and normalized intensity  $\mu = 0.8$  [50]. At pressures below 15 GPa or above 30 GPa one can see a relatively weak linear higher-energy shift of the absorption edge with increasing pressure without changing line shape. Such shift was well studied in  $\text{RMnO}_3$  as a physical pressure effect due to shortening Mn-O bond length under pressure [54-56]. On the other hand, there is an abrupt higher-energy shift from 20.2 to 29.3 GPa accompanying a variation of spectral profile, indicating the changes of valence state and crystal structure as shown later. After subtracting the physical pressure effect, the pressure dependent energy shift relative to 0.2 GPa as presented in Fig. 4b (left scale) reflects a change of valence state of Co in  $\text{PbCoO}_3$ . One can see a considerable energy shift by about  $1.1 \pm 0.1$  eV from 15 GPa to 30 GPa. As a reference, when the valence change from  $\text{Co}^{2+}$  to  $\text{Co}^{3+}$ , the energy shift is about 2.5 eV [52]. The observed Co- $K$  edge energy shift in  $\text{PbCoO}_3$  suggests the average valence change by about 0.5 (*i.e.*, from  $\text{Co}^{2.5+}$  to  $\text{Co}^{3.0+}$  in average), as illustrated in Fig. 4b (right scale). To fulfil charge balance requirement, one expects some  $\text{Pb}^{4+}$  changing to  $\text{Pb}^{2+}$  correspondingly.

Fig. 4c presents the pressure dependent Pb- $L_3$  XAS spectra of  $\text{PbCoO}_3$ . Unlike the XAS spectra at the transition metal  $L$  and  $K$  edges, where the energy positions of the strong white line and the absorption edge are very sensitive to the number of localized  $d$  valence electrons, at the Pb- $L$  edge there is no clear white line and energy position. Moreover, the Pb- $L$  absorption edge is strongly affected by crystal structure, so it is less sensitive to the Pb valence state. Therefore it is not a trivial matter to determine the Pb valence state by using the chemical shift of the absorption edge. Fortunately, the Pb- $L_3$  XAS spectrum taken from the high resolution partial fluorescence yield (PFY) mode provides an opportunity to identify the valence state of Pb. As shown in Fig. 4c, one finds that there is a sharp lower energy shoulder  $S_d$  at 13,030 eV in the PFY spectrum. This lower energy pre-edge peak is assigned to the dipole allowed transition from the  $2p^{3/2}$  core level to the unoccupied  $6s$  states, while the main peak at

13,040 eV are assigned to the transitions from the  $2p^{3/2}$  core level to the empty Pb-6d  $t_{2g}$  and  $e_g$  states, respectively [57, 58]. It was found that the pre-edge peak  $S_d$  can be observed for  $Pb^{4+}$  ion with two 6s holes, but is absent for  $Pb^{2+}$  ion with fully occupied 6s states. Thus, the spectral intensity of the pre-edge peak  $S_d$  represents the number of 6s holes and can be used to determine the valence change of Pb as a function of pressure. After subtracting the background (see the pink dash curve in Fig. 4c) originated from the edge jump and the Pb-5d states [59], the spectral integral area of  $S_d$  as a function of pressure is presented in Fig. 4d. The sharp reducing intensity with pressure going from 15 GPa to 30 GPa indicates the valence decrease of Pb. Given the initial average valence state of  $Pb^{3.5+}$  at lower pressure ( $Pb^{2+}Pb^{4+}_3Co^{2+}_2Co^{3+}_2O_{12}$ ), the relative variation of the integral area of  $S_d$  suggests the change from  $Pb^{3.5+}$  to  $Pb^{3.0+}$ . The Co-K edge ( $Co^{2.5+} \rightarrow Co^{3.0+}$ ) and Pb-L edge ( $Pb^{3.5+} \rightarrow Pb^{3.0+}$ ) XAS spectra thus confirm the  $Pb^{4+}$ - $Co^{2+}$  intermetallic charge transfer which sets in around 15 GPa with a sharp change near 20 GPa and finishes at about 30 GPa. It should be noted that Ni-K and Bi- $L_3$  XAS was used to confirm the pressure induced intermetallic charge transfer transition in  $BiNiO_3$  as well [60].

To get deeper insight into the structural features during the spin state and metal-insulator transitions as well as the Pb-Co intermetallic charge transfer, high-pressure SXRD was carried out. Fig. 5a shows the room-temperature SXRD patterns obtained at different pressures. With increasing pressure to 18.8 GPa, all the diffraction peaks systematically shift towards higher angle as expected from the volume contraction, and there is no visible trace for structural phase transition. Therefore, the A- and B-site ordered  $Pn-3$  cubic crystal structure with a  $2a_p \times 2a_p \times 2a_p$  supercell remains unchanged during the HS-LS transition of  $Co^{2+}$  (where  $a_p$  is the lattice parameter for a simple cubic  $ABO_3$  perovskite). This can also account for the electrical insulating behavior observed below 20 GPa shown in Fig. 2a. Once the room-temperature metallization takes place between 20 and 30 GPa (Fig. 2c), a new high-pressure phase (Tetra.-I phase) appears in this pressure range. As shown in Fig.

5a, the SXRD pattern collected at 21.2 GPa displays essentially different profile from that measured at 18.8 GPa. For example, the single (220) peak around  $2\theta = 10.8^\circ$  in the cubic  $Pn-3$  phase separates into two sharp diffraction peaks (400) and (222) in the Tetra.-I phase. Although the data can be indexed with a  $2\sqrt{2}a_p \times 2\sqrt{2}a_p \times 2a_p$  tetragonal unit cell and possible space groups of  $P4_2$  (No. 77),  $P4_2/m$  (No. 84), or  $P4_222$  (No. 93), we cannot determine the exact crystal structure (symmetry and atomic positions) for the new Tetra.-I phase because of the unreliable intensity ratio caused by the limited number of particles in a small space of DAC. However, Le Bail fitting was conducted to understand the structural variations. As shown in Fig. 5b, during the structural phase transition from the cubic  $Pn-3$  to the Tetra.-I phase around 20 GPa, the normalized  $a$ -axis lattice constant expands whereas the  $c$ -axis shrinks. Moreover, the  $c/a$  ratio experiences a steep drop (Fig. 5c). If the cell volume normalized to each formula unit is plotted as a function of pressure (Fig. 5d), a considerable volume collapse is found to occur by about 1.76% at 20 GPa, implying that the structural transition is first-order in nature. The presence of coexisting two phases (cubic and Tetra.-I) at 19.7 GPa and 300 K supports the first-order transition (see Fig. S3).

When the pressure further increases to 29.5 GPa at RT, a second crystal structure phase transition (Tetra.-II phase) takes place as presented in Fig. 5a and b. Le Bail analysis indicates another tetragonal lattice for this new phase with a  $2a_p \times 2a_p \times 2a_p$  supercell with possible space groups of  $P4_2mc$  (No. 105),  $P-42c$  (No. 112) or  $P4_2/mmc$  (No. 131). During the structural transition from the Tetra.-I to II phase, the normalized  $a$ -axis is reduced in a large degree while the  $c$ -axis expands slightly (Fig. 5c). As a result, the  $c/a$  ratio increases remarkably. As seen from the relationship between pressure and the normalized cell volume in Fig. 5d, the volume also experiences a discontinuous change from the Tetra.-I to II phase by about 1.12% at 30 GPa. The discontinuous decrease in the unit cell volume and the coexisting two phases (Tetra.-I and II) at 29.5 GPa indicate that the Tetra.-I to II phase transition is also first order (see Fig. S3). Since charge transfer essentially changes the charge

states and electronic configurations for two different metals, it usually leads to drastic magnetic and electrical variations as well as a sharp first-order structural phase transition, as reported in La/BiCu<sub>3</sub>Fe<sub>4</sub>O<sub>12</sub>, BiNiO<sub>3</sub> and PbCrO<sub>3</sub> [28-29,38,61-64]. The Tetra.-I to II transition of PbCoO<sub>3</sub> is also from the Pb<sup>4+</sup>-Co<sup>2+</sup> intermetallic charge transfer.

As shown in Fig. 5e, the pressure dependence of cell volume for the three structural phases at RT can be well fitted by the isothermal Birch-Murnaghan equation of state with the function  $P(V) = 1.5B_0[(V_0/V)^{7/3}-(V_0/V)^{5/3}] \times \{1+0.75(B_0'-4)[(V_0/V)^{2/3}-1]\}$ , where the  $B_0$  and  $B_0'$  are the bulk modulus and its pressure derivative, respectively [65,66]. In the case of  $B_0' = 4$ , which is a typical value for elastic lattices, the fitting gives  $B_0 = 164(3)$  GPa for the cubic  $Pn-3$  phase,  $187(8)$  GPa for the Tetra.-I phase, and  $203(3)$  GPa for the Tetra.-II phase. The value of  $B_0$  in the cubic phase of PbCoO<sub>3</sub> is similar with that observed in the simple cubic perovskite SrCoO<sub>3</sub> [67].

As seen from the temperature dependent electrical measurements at different pressures (Fig. 2), the high-pressure Tetra.-I phase is metallic whereas the Tetra.-II phase is insulating. Moreover, for the Tetra.-I phase occurring between about 20 and 30 GPa, lowering temperature triggers a metal-to-insulator transition. To understand the origin of this MI transition, low-temperature SXR D was performed at different pressures. As shown in Figure S4, at a pressure near 22 GPa, one finds that the insulating Tetra.-II phase emerges and coexists with the metallic Tetra.-I phase at temperatures below  $T_{MI}$  (e.g. at 150 and 100 K). As the pressure increases to about 27 GPa, these two tetragonal phases coexist at higher temperatures such as 200 K. These observations indicate that lowering temperature favors the Pb<sup>4+</sup>-Co<sup>2+</sup> charge transfer as well as the formation of the insulating Tetra.-II phase, giving rise to the metal-to-insulator transition with unusual  $T_{MI}$  shift. One may notice that the phase boundary determined by SXR D study doesn't agree well with the M-I transition observed at 21 GPa and 214 K (see phase diagram shown later). It is most probably owing to the presence of temperature/pressure hysteresis at the first-order Tetra.-I to

Tetra.-II transition as evidenced in the wide two phases coexisting region. The SXRD data points at 200 K were collected by pressure scan measurements at a constant temperature while the resistivity measurement were conducted on heating at a constant pressure. Although the exact structural determination for both high-pressure phases remains for future resolution, the present pressure and temperature dependent SXRD results reveal significant structural variations accompanying with the pressure-induced metallization and the Pb-Co intermetallic charge transfer in  $\text{PbCoO}_3$ .

On the basis of the peculiar charge combination and crystal constitution, we now discuss the origin for the sensitive pressure dependence of the spin and charge states in  $\text{PbCoO}_3$ , as schematically shown in Fig. 6. At ambient pressure,  $\text{PbCoO}_3$  has a  $\text{Pb}^{2+}\text{Pb}^{4+}_3\text{Co}^{2+}_2\text{Co}^{3+}_2\text{O}_{12}$  charge format as well as the A- and B-site ordered perovskite structure. Usually, a considerable charge difference ( $\geq 2$ ) is needed between the B- and B'-site cations to form an ordered perovskite structure [68]. In the case of  $\text{PbCoO}_3$ , it is the large ionic size discrepancy between the HS  $\text{Co}^{2+}$  and LS  $\text{Co}^{3+}$  that stabilizes the rocksalt-type ordered perovskite structure, although the charge difference is only 1. In most  $\text{ABO}_3$  perovskites with the average B-O-B bond angle larger than  $160^\circ$ , the pressure induced volume shrinking is mainly attributed to the  $\text{BO}_6$  octahedral tilting and/or rotation in addition to the B-O bond length decrease. In the current  $\text{PbCoO}_3$ , however, the initial  $\text{Co}^{2+}\text{-O-Co}^{3+}$  bond angle has already decreased to about  $140^\circ$  to fill the small-size  $\text{Pb}^{4+}$  into the perovskite A-site. As a result, when the compound encounters external physical pressure, the  $\text{Co}^{2+}\text{O}_6$  octahedra with significantly longer Co-O bond length than that of  $\text{Co}^{3+}\text{O}_6$  have to reduce the volume by majorly decrease the  $\text{Co}^{2+}\text{-O}$  distance (see Fig. S2), giving rise to remarkable increase of  $\text{Co}^{2+}\text{O}_6$  octahedral crystal field energy. Since the crystal field overcomes the Hund coupling energy, the high spin state of  $\text{Co}^{2+}$  changes to low spin. Therefore, a continuous HS-LS transition is found to occur in  $\text{PbCoO}_3$  at pressure below 15 GPa, which is responsible for the unusual increase of resistance with pressure because the electronic density of state of  $\text{PbCoO}_3$  near the Fermi surface is dominated by  $\text{Co}^{2+}$  [37]. In

addition, first-principle calculations show that there exist visible hybridization between  $\text{Pb}^{4+}$  and  $\text{Co}^{2+}$  at ambient pressure, indicating that the empty  $6s$  orbitals of  $\text{Pb}^{4+}$  have similar energy level with that of the  $e_g$  orbitals of  $\text{Co}^{2+}$  [37]. As mentioned above, high pressure increases the crystal field energy and induces the HS-LS transition of  $\text{Co}^{2+}$ . Correspondingly, the enhanced crystal field will also lift the energy level of the  $e_g$  orbitals. Thus, following the HS-LS transition, it is energetically favorable for electrons transfer from the  $e_g$  orbitals of  $\text{Co}^{2+}$  to the  $6s$  orbitals of  $\text{Pb}^{4+}$  under higher pressure, as we observed in experiment by the continuous  $\text{Pb}^{4+}$ - $\text{Co}^{2+}$  intermetallic charge transfer between 15 and 30 GPa. Since the charge transfer decreases the component of  $\text{Co}^{2+}$  and therefore reduces the average ionic radius at this atomic site, the accumulated effect of charge transfer eventually breaks the B-site ordered perovskite structure to a disordered one, resulting in the first-order structure phase transition as well as the metallization with pressure up to 20 GPa near RT. Once the charge transfer completes at about 30 GPa, all the LS  $\text{Co}^{2+}$  changes to the LS  $\text{Co}^{3+}$  with  $S = 0$ . As a consequence, the compound displays another first-order structure transition and reenters an electrical insulating state. In addition to external pressure, lowering temperature also favors the  $\text{Pb}^{4+}$ - $\text{Co}^{2+}$  intermetallic charge transfer, leading to the coexistence of the insulating Tetra.-II phase and the metallic Tetra.-I between 20 and 30 GPa at lower temperatures.

#### 4. CONCLUSIONS

According to the high-pressure resistance, XES, XAS and SXRD results described above, we obtain an interesting pressure and temperature dependent phase diagram for  $\text{PbCoO}_3$  as shown in Fig. 7. i) Below  $\sim 20$  GPa, the compound maintains the A- and B-site ordered quadruple perovskite structure in the cubic  $Pn-3$  symmetry with the charge combination of  $\text{Pb}^{2+}\text{Pb}^{4+}_3\text{Co}^{2+}_2\text{Co}^{3+}_2\text{O}_{12}$  ( $\text{Pb}^{3.5+}\text{Co}^{2.5+}\text{O}_3$  in average). However, the HS state of  $\text{Co}^{2+}$  sensitively depends on external pressure. It sluggishly changes to a LS state with increasing pressure up to about 15 GPa. When the spin state transition

finishes, pressure induced intermetallic charge transfer starts to occur between  $\text{Co}^{2+}$  and  $\text{Pb}^{4+}$  ions, leading to essentially different electrical transport properties at pressures below and above 15 GPa. ii) Between approximate 20 and 30 GPa, metallization is observed due to the accumulated effect of  $\text{Pb}^{4+}$ - $\text{Co}^{2+}$  charge transfer near RT, strongly suggesting the melting of the ordered low-spin  $\text{Co}^{2+}$  and  $\text{Co}^{3+}$  states into a mixed  $\text{Co}^{2.5+}$  in average. This is consistent with the first-order structural phase transition to the Tetra.-I phase. The  $\text{Pb}^{4+}$ - $\text{Co}^{2+}$  charge transfer still takes place in the Tetra.-I phase, making the LS- $\text{Co}^{2+}$  state be oxidized to the LS- $\text{Co}^{3+}$  one. Since the composition of the strongly insulating LS- $\text{Co}^{3+}$  is enhanced by the charge transfer, the  $T_{\text{MI}}$  of  $\text{PbCoO}_3$  exhibits an unusual shift towards higher temperatures on compression. Moreover, at fixed pressure in this phase, lowering temperature favors the  $\text{Pb}^{4+}$ - $\text{Co}^{2+}$  ICT as well as the formation of the insulating Tetra.-II phase, which is responsible for the observed low-temperature MI transition. iii) With pressure up to  $\sim 30$  GPa at RT, the Pb-Co intermetallic charge transfer completes, changing the charge combination to be  $\text{Pb}^{3.0+}\text{Co}^{3.0+}\text{O}_3$  in average. Accordingly, the compound experiences another first-order structure phase transition toward the Tetra.-II phase with considerable volume shrinking. In the Tetra.-II phase, all the transition-metal sites are occupied by the LS- $\text{Co}^{3+}$  with  $S = 0$ . Therefore, electrical insulating behavior shows again in the whole temperature region we measured. The present  $\text{PbCoO}_3$  provides the first example where spin state, charge state, crystal structure, and metal-insulator transitions take place collectively in the same material system, opening up a new avenue for study sequential spin state transition and intermetallic charge transfer as well as related multifunctional transformations.

## ■ ASSOCIATED CONTENT

### Supporting Information

Refined structural parameters for  $\text{PbCoO}_3$  at 290 K under various pressures based on the neutron powder diffraction; Electrical transport properties of  $\text{PbCoO}_3$  during pressure release from 48.9 to 1.6 GPa; Pressure dependence of the average bond lengths calculated from the structural parameters determined by Rietveld analysis of neutron diffraction data; Synchrotron X-ray diffraction (SXR) patterns measured at different pressures and temperatures.

## ■ AUTHOR INFORMATION

### Corresponding Authors

\*jmchen@nsrrc.org.tw

\*mazuma@mssl.titech.ac.jp

\*ywlong@iphy.ac.cn

### Present Addresses

#Université Lille, CNRS, Centrale Lille, ENSCL, Université Artois, UMR 8181–UCCS–Unité de Catalyse et Chimie du Solide, F-59000 Lille, France

## ■ ACKNOWLEDGMENTS

The authors thank Y. F. Yang and Y. Y. Cao for fruitful discussion. This work was supported by the National Key R&D Program of China (Grant No. 2018YFE0103200, 2018YFA0305700), the National Natural Science Foundation of China (Grant No. 11934017, 51772324, 11574378), the Chinese Academy of Sciences (Grant No. QYZDB-SSW-SLH013, GJHZ1773, YZ201555), the Ministry of Science and Technology (Grant No. MOST 105-2113-M-213 -005 -MY3), JSPS KAKENHI Grant Numbers, JP18H05208, and JP19H05625, from the Japan Society for the Promotion of Science (JSPS) and JSPS and CAS under the Japan-China Scientific Cooperation Program. Y. Long was partially supported by World Research Hub Initiative, Institute of Innovative Research, Tokyo Institute of Technology and Collaborative Research Projects, Laboratory for Materials and Structures, Tokyo Institute of Technology. The synchrotron-radiation X-ray diffraction experiments were performed using a QST experimental station at JAEA beamline BL22XU, SPring-8 with the approval of the Japan Synchrotron Radiation Research Institute (Proposal Nos. 2016A3784, 2017A3781, 2018A3782, 2019A3781, and 2019B3781), and were supported by QST Advanced Characterization Nanotechnology Platform under the remit of “Nanotechnology Platform” of the Ministry of Education, Culture, Sports, Science and Technology, Japan (Proposal Nos. A-16-QS-0011, A-17-QS-0010, A-18-QS-0014, A-19-QS-0015, and A-19-QS-0039).

## ■ REFERENCES

- (1) Keimer, B.; Kivelson, S. A.; Norman, M. R.; Uchida, S.; Zaanen, J. From quantum matter to high-temperature superconductivity in copper oxides. *Nature* 2015, 518, 179.
- (2) Imada, M.; Fujimori, A.; Tokura, Y. Metal-insulator transitions. *Rev. Mod. Phys.* 1998, 70, 1039 – 1263.
- (3) Elbio, D.; Takashi, H.; Adriana, M. Colossal magnetoresistant materials: the key role of phase separation. *Phys. Rep.* 2001, 344, 1-153.
- (4) Salamon, M. B.; Jaime, M. The physics of manganites: structure and transport. *Rev. Mod. Phys.* 2001, 73, 583 – 628.
- (5) Hemberger, J.; Lobina, S.; Krug von Nidda, H.-A.; Tristan, N.; Ivanov, V. Y.; Mukhin, A. A.; Balbashov, A. M.; Loidl, A. Complex interplay of 3d and 4f magnetism in  $\text{La}_{1-x}\text{Gd}_x\text{MnO}_3$ . *Phys. Rev. B* 2004, 94, 024414.
- (6) Seo, J. S.; Whang, D.; Lee, H.; Jun, S. I.; Oh, J.; Jeon, Y. J.; Kim, K. A homochiral metal – organic porous material for enantioselective separation and catalysis. *Nature* 2000, 404, 982 – 986.
- (7) Tokura, Y.; Seki, S.; Nagaosa, N. Multiferroics of spin origin. *Rep. Prog. Phys.* 2014, 77 076501.
- (8) Wang, X.; Chai, Y. S.; Zhou, L.; Cao, H. B.; Cruz, C.-D.; Yang, J. Y.; Dai, J. H.; Yin, Y. Y.; Yuan, Z.; Zhang, S.; Yu, R. Z.; Azuma, M.; Shimakawa, Y.; Zhang, H. M.; Dong, S.; Sun, Y.; Jin, C. Q.; Long, Y. W. Observation of Magnetoelectric Multiferroicity in a Cubic Perovskite System:  $\text{LaMn}_3\text{Cr}_4\text{O}_{12}$ . *Phys. Rev. Lett.* 2015, 115, 087601.
- (9) Zhou, L.; Dai, J. H.; Chai, Y. S.; Zhang, H. M.; Dong, S.; Cao, H. B.; Calder, S.; Yin, Y. Y.; Wang, X.; Shen, X. D.; Liu, Z. H.; Saito, T.; Shimakawa, Y.; Hojo, H.; Ikuhara, Y.; Azuma, M.; Hu, Z. W.; Sun, Y.; Jin, C. Q.; Long, Y. W. Realization of

Large Electric Polarization and Strong Magnetoelectric Coupling in  $\text{BiMn}_3\text{Cr}_4\text{O}_{12}$ . *Adv. Mater.* 2017, 29, 201703435.

(10) Haverkort, M. W.; Hu, Z.; Cezar, J. C.; Burnus, T.; Hartmann, H.; Reuther, M.; Zobel, C.; Lorenz, T.; Tanaka, A.; Brookes, N. B.; Hsieh, H. H.; Lin, H.-J.; Chen, C. T.; Tjeng, L. H. Spin State Transition in Studied Using Soft X-ray Absorption Spectroscopy and Magnetic Circular Dichroism. *Phys. Rev. Lett.* 2006, 97, 176405.

(11) Zobel, C.; Kriener, M.; Bruns, D.; Baier, J.; Grüninger, M.; Lorenz, T.; Reutler, P.; Revcolevschi, A. Evidence for a low-spin to intermediate-spin state transition in  $\text{LaCoO}_3$ . *Phys. Rev. B* 2005, 71, 019902.

(12) Křápek, V.; Novák, P.; Kuneš, J.; Novoselov, D.; Korotin, D. M.; Anisimov, V. I. Spin state transition and covalent bonding in  $\text{LaCoO}_3$ . *Phys. Rev. B* 2012, 86, 195104.

(13) Altarawneh, M. M.; Chern, G.-W.; Harrison, N.; Batista, C. D.; Uchida, A.; Jaime, M.; Rickel, D. G.; Crooker, S. A.; Mielke, C. H.; Betts, J. B.; Mitchell, J. F.; Hoch, M. J. R. Cascade of Magnetic Field Induced Spin Transitions in  $\text{LaCoO}_3$ . *Phys. Rev. Lett.* 2012 109, 037201.

(14) Ikeda, A.; Nomura, T.; Matsuda, Y. H.; Matsuo, A.; Kindo, K.; Sato, K. Spin state ordering of strongly correlating  $\text{LaCoO}_3$  induced at ultrahigh magnetic fields. *Phys. Rev. B* 2016, 93, 220401(R).

(15) Chakrabarti, B.; Birol, T.; Haule, K. Role of entropy and structural parameters in the spin-state transition of  $\text{LaCoO}_3$ . *Phys. Rev. Materials* 2017, 1, 064403.

(16) Klie, R. F.; Zheng, J. C.; Zhu, Y.; Varela, M.; Wu, J.; Leighton, C. Direct Measurement of the Low-Temperature Spin-State Transition in  $\text{LaCoO}_3$ . *Phys. Rev. Lett.* 2007, 99, 047203.

(17) Vankó, G.; Rueff, J. P.; Mattila, A.; Németh, Z.; Shukla, A. Temperature- and pressure-induced spin-state transitions in  $\text{LaCoO}_3$ . *Phys. Rev. B* 2006, 73, 024424.

(18) Mattila, A.; Rueff, J-P.; Badro, J.; Vankó, G.; Shukla, A. Metal-ligand interplay in

strongly correlated oxides: A parametrized phase diagram for pressure-induced spin transitions. *Phys. Rev. Lett.* 2007, 98, 196404.

(19) Lengsdorf, R.; Rueff, J.-P.; Vankó, G.; Lorenz, T.; Tjeng, L. H.; Abd-Elmeguid, M. M. Spin-state-driven metal-insulator transition in (La,Sr)CoO<sub>3</sub> under high-pressure. *Phys. Rev. B* 2007, 75, 180401(R).

(20) Kim, B.; Kim, K.; Min, B. I. Universal metastability of the low-spin state in Co<sup>2+</sup> systems: Non-Mott type pressure-induced spin-state transition in CoCl<sub>2</sub>. *Phys. Rev. B* 2014, 89, 115131.

(21) Ding, Y.; Fernandez-Rodriguez, J.; Kim, J.; Li, F. F.; Casa, D.; Upton, M.; Gog, T.; Mao, H-K; Veenendaal, M. V. Spin-ordering mediated orbital hybridization in CoO at high pressures. *Phys. Rev. B* 2012, 86, 094107.

(22) Leonov, I.; Ponomareva, A. V.; Nazarov, R.; Abrikosov, I. A. Pressure-induced spin-state transition of iron in magnesiowüstite (Fe,Mg)O. *Phys. Rev. B* 2017, 96, 075136.

(23) Lin, J-F.; Gavriliuk, A. G.; Struzhkin, V. V.; Jacobsen, S. D.; Sturhahn, W.; Hu, M. Y.; Chow, P.; Yoo, C-S. Pressure-induced electronic spin transition of iron in magnesiowustite-(Mg,Fe)O. *Phys. Rev. B* 2006, 73, 113107.

(24) Javaid, S.; Akhtar, M. J.; Ahmad, I.; Younas, M.; Shah, S. H.; Ahmad, I. Pressure driven spin crossover and isostructural phase transition in LaFeO<sub>3</sub>. *Journal of Applied Physics* 2013, 114, 243712.

(25) Takano, M.; Nasu, S.; Abe, T.; Yamamoto, K.; Endo, S.; Takeda, Y.; Goodenough, J. B. Pressure-induced high-spin to low-spin transition in CaFeO<sub>3</sub>. *Phys. Rev. Lett.* 2001, 67, 3267.

(26) Kuneš, J.; Lukoyanov, A. V.; Anisimov, V. I.; Scalettar, R. T.; Pickett, W. E. Collapse of magnetic moment drives the Mott transition in MnO. *Nature Materials* 2008, 7, 198 – 202.

- (27) Long, Y. W.; Hayashi, N.; Saito, T.; Azuma, M.; Muranaka, S.; Shimakawa, Y. Temperature-induced A - B intersite charge transfer in an A-site-ordered  $\text{LaCu}_3\text{Fe}_4\text{O}_{12}$  perovskite. *Nature* 2009, 458, 60.
- (28) Long, Y. W.; Kawakami, T.; Chen, W. T.; Saito, T.; Watanuki, T.; Nakakura, Y.; Liu, Q. Q.; Jin, C. Q.; Shimakawa, Y. Pressure Effect on Intersite Charge Transfer in A-site-Ordered Double-Perovskite-Structure Oxide. *Chem. Mater.* 2012, 24, 2235–2239.
- (29) Azuma, M.; Carlsson, S.; Rodgers, J.; Tucker, M. G.; Tsujimoto, M.; Ishiwata, S.; Isoda, S.; Shimakawa, Y.; Takano, M.; Atfield, J. P. Pressure-Induced Intermetallic Valence Transition in  $\text{BiNiO}_3$ . *J. Am. Chem. Soc.* 2007, 129, 14433-14436.
- (30) Guillou, F.; Kummer, K.; Bréard, Y.; Hervé, L.; Hardy, V. Valence and spin-state transition in cobaltates revisited by x-ray magnetic circular dichroism. *Phys. Rev. B* 2017, 95, 174445.
- (31) Hejtmánek, J.; Šantavá, E.; Knížek, K.; Maryško, M.; Jirák, Z. Metal-insulator transition and the  $\text{Pr}^{3+}/\text{Pr}^{4+}$  valence shift in  $(\text{Pr}_{1-y}\text{Y}_y)_{0.7}\text{Ca}_{0.3}\text{CoO}_3$ . *Phys. Rev B* 2010, 82, 165107.
- (32) Guillou, F.; Zhang, Q.; Hu, Z.; Kuo, C. Y.; Chin, Y. Y.; Lin, H. J.; Chen, C. T.; Tanaka, A.; Tjeng, L. H.; Hardy, V. Coupled valence and spin state transition in  $(\text{Pr}_{0.7}\text{Sm}_{0.3})_{0.7}\text{Ca}_{0.3}\text{CoO}_3$ . *Phys. Rev B* 2013, 87, 115114.
- (33) Chen, J. M.; Lee, J. M.; Haw, S. C.; Chen, S. A.; Hardy, V.; Guillou, F.; Chen, S. W.; Kuo, C. Y.; Pao, C. W.; Lee, J. F.; Hiraoka, N.; Ishii, H.; Tsuei, K. D.; Hu, Z. Evolution of spin and valence states of  $(\text{Pr}_{0.7}\text{Sm}_{0.3})_{0.7}\text{Ca}_{0.3}\text{CoO}_3$  at high temperature and high pressure. *Phys. Rev B* 2014, 90, 035107.
- (34) García-Munoz, G. L.; Frontera, G.; Baron-Gonzalez, A. J.; Valencia, S.; Blasco, J.; Feyerherm, R.; Dudzik, E.; Abrudan, R.; Radu, F. Valence transition in  $(\text{Pr,Ca})\text{CoO}_3$  cobaltites: Charge migration at the metal-insulator transition. *Phys. Rev B* 2011, 84,

045104.

(35) Hejtmanek, J.; Jirak, Z.; Kaman, O.; Knizek, K.; Santava, E.; Nitta, K.; Naito, T.; Fujishiro, H. Phase transition in  $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{CoO}_3$  and related cobaltites. *Eur. Phys. J. B* 2013, 86, 305.

(36) Fujita, T.; Miyashita, T.; Yasui, Y.; Kobayashi, Y.; Sato, M.; Nishibori, E.; Sakata, M.; Shimojo, Y.; Igawa, N.; Ishii, Y.; Kakurai, K.; Adachi, T.; Ohishi, Y.; Takata, M. Transport and Magnetic Studies on the Spin State Transition of  $\text{Pr}_{1-x}\text{Ca}_x\text{CoO}_3$  up to High Pressure. *J. Phys. Soc. Jpn.* 2004, 73, 1987-1997.

(37) Sakai, Y.; Yang, J. Y.; Yu, R. Z.; Hojo, H.; Yamada, I.; Miao, P.; Lee, S.; Torii, S.; Kamiyama, T.; Ležaić, M.; Bihlmayer, G.; Mizumaki, M.; Komiyama, J.; Mizokawa, T.; Yamamoto, H.; Nishikubo, T.; Hattori, Y.; Oka, K.; Yin, Y. Y.; Dai, J. H.; Li, W. M.; Ueda, S.; Aimi, A.; Mori, D.; Inaguma, Y.; Hu, Z. W.; Uozumi, T.; Jin, C. Q.; Long, Y. W.; Azuma, M. A-Site and B-Site Charge Orderings in an s - d Level Controlled Perovskite Oxide  $\text{PbCoO}_3$ . *J. Am. Chem. Soc.* 2017, 139, 4574–4581.

(38) Huang, L. Y.; Wang, L.; Dai, X. Pressure-driven orbital selective insulator-to-metal transition and spin-state crossover in cubic  $\text{CoO}$ . *Phy. Rev. B* 2012, 85, 245110.

(39) Feng L.; Wei L.; Feng, J. S.; Xiang, H. J. Genetic algorithm prediction of pressure-induced multiferroicity in the perovskite  $\text{PbCoO}_3$ , *Phy. Rev. B* 2019, 99, 205104.

(40) Zhang, J. L.; Zhang, S. J.; Weng, H. M.; Zhang, W.; Yang, L. X.; Liu, Q. Q.; Feng, S. M.; Wang, X. C.; Yu, R. C.; Cao, L. Z.; Wang, L.; Yang, W. G.; Liu, H. Z.; Zhao, W. Y.; Zhang, S. C.; Dai, X.; Fang, Z.; Jin, C. Q. Pressure-induced superconductivity in topological parent compound  $\text{Bi}_2\text{Te}_3$ . *Proc. Natl. Acad. Sci.* 2011, 108, 24.

(41) Mao, H. K.; Xu, J.; Bell, P. M. Calibration of the ruby pressure gauge to 800 kbar

- under quasi - hydrostatic conditions. *J. Geophys. Res.* 1986, 91, 4673.
- (42) Chen, J. M.; Chin, Y. Y.; Valldor, M.; Hu, Z. W.; Lee, J. M.; Haw, S. C.; Hiraoka, N.; Ishii, H.; Pao, C. W.; Tsuei, K. D.; Lee, J. F.; Lin, H. J.; Jang, L. Y.; Tanaka, A.; Chen, C. T.; Tjeng, L. H. A Complete High-to-Low spin state Transition of Trivalent Cobalt Ion in Octahedral Symmetry in  $\text{SrCo}_{0.5}\text{Ru}_{0.5}\text{O}_{3-\delta}$ . *J. Am. Chem. Soc.* 2014, 136(4), 1514 - 1519.
- (43) Izumi, F.; Momma, K. Three-dimensional visualization in powder diffraction. *Solid State Phenom.* 2007, 130, 15 - 20.
- (44) Besson, J. M.; Nelmes, R. J.; Hamel, G.; Loveday, J. S.; Weill, G.; Hull, S. Neutron powder diffraction above 10 GPa. *Physica B* 1992, 180, 907.
- (45) Larson, A. C.; Dreele, V.; General, R. B. Structural Analysis System (GSAS); Los Alamos National Laboratory Report; Los Alamos National Laboratory: Los Alamos, NM 2000, 86-748.
- (46) Chang, C. F.; Hu, Z.; Wu, H.; Burnus, T.; Hollmann, N.; Benomar, M.; Lorenz, T.; Tanaka, A.; Lin, H.-J.; Hsieh, H. H.; Chen, C. T.; Tjeng L. H. Spin Blockade, Orbital Occupation, and Charge Ordering in  $\text{La}_{1.5}\text{Sr}_{0.5}\text{CoO}_4$ . *Phys. Rev. Lett.* 2009, 102, 116401.
- (47) Tsutsumi, K.; Nakamori, H.; Ichikawa, K. X-ray Mn  $K_{\beta}$  emission spectra of manganese oxides and manganates. *Phys. Rev. B* 1976, 13, 929 - 933.
- (48) Vankó, G.; Neisius, T.; Molnár, G.; Renz, F.; Kárpáti, S.; Shukla, A.; de Groot, F. M. F. Probing the 3d Spin Momentum with X-ray Emission Spectroscopy: The Case of Molecular-Spin Transitions. *J. Phys. Chem. B* 2006, 110, 11647.
- (49) Chin, Y. Y.; Lin, H. J.; Hu, Z. W.; Kuo, C. Y.; Mikhailova, D.; Lee, J. M.; Haw, S. C.; Chen, S. A.; Schnelle, W.; Ishii, H.; Hiraoka, N.; Liao, Y. Y.; Tsuei, K. D.; Tanaka, A.; Tjeng, L. H.; Chen, C. T.; Chen, J. M. Relation between the Co-O bond lengths and the spin state of Co in layered cobaltates: a high-pressure study. *Sci. Rep.* 2017, 7,

3656.

(50) Chen, J. M.; Lee, J. M.; Haw, S. C.; Chen, S. A.; Hardy, V.; Guillou, F.; Chen, S. W.; Kuo, C. Y.; Pao, C. W.; Lee, J. F.; Hiraoka, N.; Ishii, H.; Tsuei, K. D.; Hu, Z. Evolution of spin and valence states of  $(\text{Pr}_{0.7}\text{Sm}_{0.3})_{0.7}\text{Ca}_{0.3}\text{CoO}_3$  at high temperature and high pressure. *Phys. Rev. B* 2014, 90, 035107.

(51) Oka, K.; Azuma, M.; Chen, W. T.; Yusa, H.; Belik, A. A.; Muromachi, E. T.; Mizumaki, M.; Ishimatsu, N.; Hiraoka, N.; Tsujimoto, M.; Tucker, M. G.; Attfield, J. P.; Shimakawa, Y. Pressure-Induced Spin-State Transition in  $\text{BiCoO}_3$ . *J. Am. Chem. Soc.* 2010, 132(27), 9438 – 9443.

(52) Yang, J. Y.; Zhou, L.; Cheng, J. G.; Hu, Z. W.; Kuo, C. Y.; Pao, C. W.; Jang, L. Y.; Lee, J. Y.; Dai, J. H.; Zhang, S. J.; Feng, S. M.; Kong, P. P.; Yuan, Z.; Yuan, J.; Uwatoko, Y.; Liu, T.; Jin, C. Q.; Long, Y. W. Charge Transfer Induced Multifunctional Transitions with Sensitive Pressure Manipulation in a Metal – Organic Framework. *Inorg. Chem.* 2015 54 (13), 6433 – 6438.

(53) Croft, M.; Sills, D.; Greenblatt, M.; Lee, C.; Cheong, S.-W.; Ramanujachary, K. V.; Tran, D. Systematic Mn d-configuration change in the  $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$  system: A Mn K-edge XAS study. *Phys. Rev. B* 1997, 55, 8726.

(54) Ramos, A. Y.; Souza-Neto, N. M.; Tolentino, H. C. N.; Bunau, O.; Joly, Y.; Grenier, S. Itié, J.-P.; Flank, A.-M.; Lagarde P.; Caneiro, A. Bandwidth-driven nature of the pressure-induced metal state of  $\text{LaMnO}_3$ . *EPL* 2011, 96, 36002.

(55) Chen, J. M.; Chou, T. L.; Lee, J. M.; Chen, S. A.; Chan, T. S.; Chen, T. H.; Lu, K. T.; Chuang, W. T.; Sheu, H.-S.; Chen, S. W.; Lin, C. M.; Hiraoka, N.; Ishii, H.; Tsuei, K. D.; Yang, T. J. Pressure-induced structural distortion of  $\text{TbMnO}_3$ : A combined x-ray diffraction and x-ray absorption spectroscopy study. *Phys. Rev. B* 2009, 79 165110.

(56) Chen, J. M.; Lee, J. M.; Chou, T. L.; Chen, S. A.; Huang, S. W.; Jeng, H. T.; Lu,

K. T.; Chen, T. H.; Liang, Y. C.; Chen, S. W.; Chuang, W. T.; Sheu, H.-S.; Hiraoka, N.; Ishii, H.; Tsuei, K. D.; Huang E.; Lin, C. M.; Yang, T. J. Pressure-dependent electronic structures in multiferroic: A combined lifetime broadening-suppressed x-ray absorption spectroscopy and ab initio electronic structure study. *J. Chem. Phys.* 2010, 133, 154510.

(57) Liang, G.; Liu, R. S.; Wang, L. V. XANES study of the valence of Pb in  $(\text{Tl}_{0.5}\text{Pb}_{0.5})\text{Sr}_2\text{Ca}_{1-x}\text{Y}_x\text{Cu}_2\text{O}_{7-\delta}$ . *Int. J. Mod. Phys. B* 1999, 13, 3693.

(58) Chen, K.; Mijiti, Y.; Agrestini, S.; Liao, S. C.; Li, X.; Zhou, J. S.; Cicco, A.; Di, B. F.; Tjeng, L. H., Hu, Z. Valence State of Pb in Transition Metal Perovskites  $\text{PbTMO}_3$  (TM = Ti, Ni) Determined From X-Ray Absorption Near-Edge Spectroscopy. *Phys. Status Solidi B* 2018, 255, 1800014.

(59) Chen, C. T.; Sette, F.; Ma, Y.; Hybertsen, M. S.; Stechel, E. B.; Foulkes, W. M. C.; Schuler, M.; Cheong, S-W.; Cooper, A. S.; Rupp, L. W.; Batlogg, J. B.; Soo, Y. L.; Ming, Z. H.; Krol, A.; Kao, Y. H. Electronic states in  $\text{La}_{2-x}\text{Sr}_x\text{CuO}_{4+\delta}$  probed by soft-x-ray absorption. *Phys. Rev. Lett.* 1991, 66, 104.

(60) Mizumaki, M.; Ishimatsu, N.; Kawamura, N.; Azuma, M.; Shimakawa, Y.; Takano, M.; Uozumi, T. Direct observation of the pressure-induced charge redistribution in  $\text{BiNiO}_3$  by x-ray absorption spectroscopy. *Phys. Rev. B* 2009, 80, 233104.

(61) Yamada, I.; Etani, H.; Tsuchida, K.; Marukawa, S.; Hayashi, N.; Kawakami, T.; Mizumaki, M.; Ohgushi, K.; Kusano, Y.; Kim, J.; Tsuji, N.; Takahashi, R.; Nishiyama, N.; Inoue, T.; Irifune, T.; Takano, M. Control of Bond-Strain-Induced Electronic Phase Transitions in Iron Perovskites. *Inorg. Chem.* 2013, 52, 13751-13761.

(62) Long, Y. W.; Shimakawa, Y. Intermetallic charge transfer between A-site Cu and B-site Fe in A-site-ordered double perovskites. *New. J. Phys.* 2010, 12, 063029.

(63) Long, Y. W.; Saito, T.; Tohyama, T.; Oka, K.; Azuma, M.; Shimakawa, Y.

Intermetallic Charge Transfer in A-Site-Ordered Double Perovskite  $\text{BiCu}_3\text{Fe}_4\text{O}_{12}$ , *Inorg. Chem.* 2009, 48, 8489-8492.

(64) Yu, R. Z.; Hojo, H.; Watanuki, T.; Mizumaki, M.; Mizokawa, T.; Oka, K.; Kim, H.; Machida, A.; Sakaki, K.; Nakamura, Y.; Agui, A.; Mori, D.; Inaguma, Y.; Schlipf, M.; Rushchanskii, K. Z.; Ležaić, M.; Matsuda, M.; Ma J.; Calder, S.; Isobe, M.; Ikuhara, Y.; Azuma, M. Melting of Pb Charge Glass and Simultaneous Pb–Cr Charge Transfer in  $\text{PbCrO}_3$  as the Origin of Volume Collapse. *J. Am. Chem. Soc.* 2015, 137, 39, 12719-12728.

(65) Murnaghan, F. D. The compressibility of media under extreme pressures, *Proc. Natl. Acad. Sci. U.S.A.* 1944, 30 (9), 244.

(66) Birch, F. Finite elastic strain of cubic crystals, *Phys. Rev.* 1947, 71, 809.

(67) Yang, J. Y.; Terakura, C.; Medarde, M.; White, J. S.; Sheptyakov, D.; Yan, X. Z.; Li, N. N.; Yang, W. G.; Xia, H. L.; Dai, J. H.; Yin, Y. Y.; Jiao, Y. Y.; Cheng, J. G.; Bu, Y. L.; Zhang, Q. F.; Li, X. D.; Jin, C. Q.; Taguchi, Y.; Tokura, Y.; Long, Y. W. Pressure-induced spin reorientation and spin state transition in  $\text{SrCoO}_3$ , *Phys. Rev. B* 2015, 92, 195147.

(68) Vasala, S.; Karppinen, M.  $\text{A}_2\text{BB}'\text{O}_6$  perovskites: A review, *Prog. Solid State Chem.* 2015, 43, 1-36.

## FIGURES AND FIGURE CAPTIONS

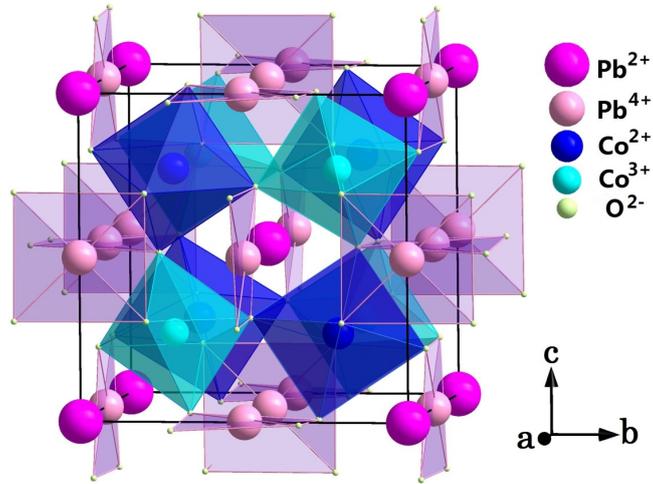


Figure 1. Schematic crystal structure of both A- and B-site ordered PbCoO<sub>3</sub> (Pb<sup>2+</sup>Pb<sup>4+</sup><sub>3</sub>Co<sup>2+</sup><sub>2</sub>Co<sup>3+</sup><sub>2</sub>O<sub>12</sub>) quadruple perovskite with *Pn-3* symmetry. The corner-sharing Co<sup>2+</sup>/Co<sup>3+</sup>O<sub>6</sub> octahedra and isolated Pb<sup>4+</sup>O<sub>4</sub> squares are shown. Atomic positions: Pb<sup>2+</sup> *2a* (0.5, 0.5, 0.5), Pb<sup>4+</sup> *6d* (0.5, 0, 0), Co<sup>2+</sup> *4b* (0.25, 0.25, 0.25), Co<sup>3+</sup> *4c* (0.75, 0.75, 0.75), O<sup>2-</sup> *24h* (*x*, *y*, *z*).

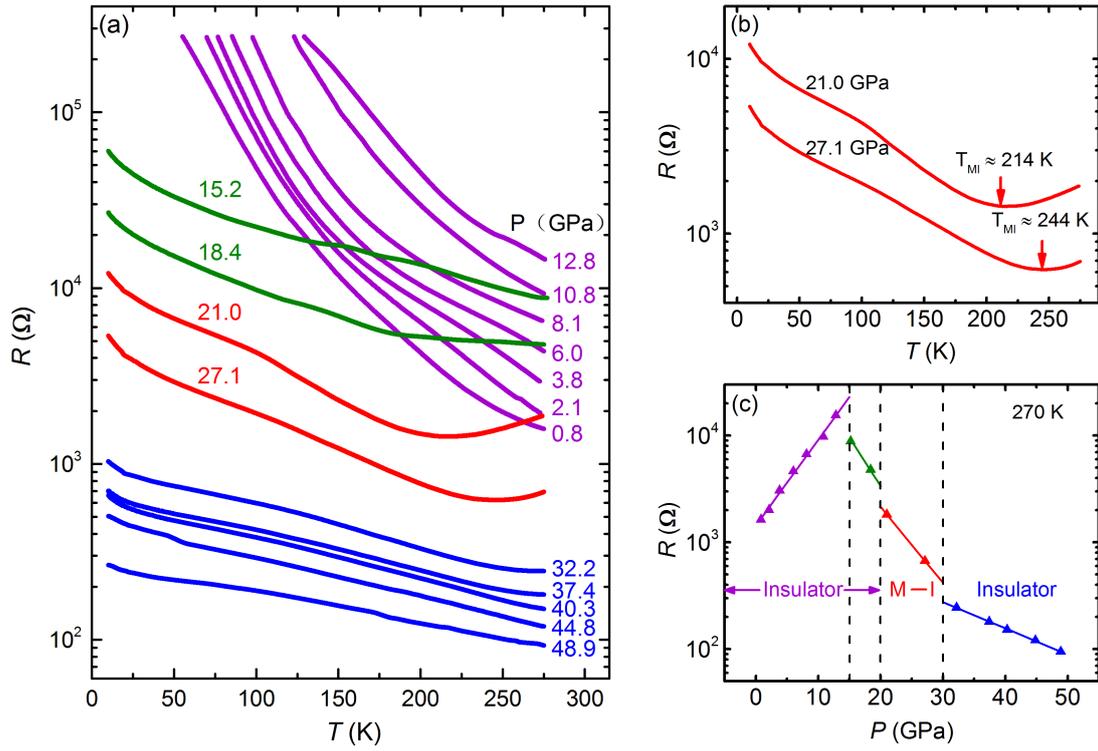


Figure 2. Electrical transport properties of  $\text{PbCoO}_3$ . (a) Temperature-dependence of resistance at different pressures. (b) Metal-insulator transitions observed at 21.0 GPa and 27.1 GPa. The  $T_{\text{MI}}$  stands for the critical temperature for the transition. (c) Resistance values under various pressures at 270 K. The triangles show the measurement data, and the lines display the linear fitting results.

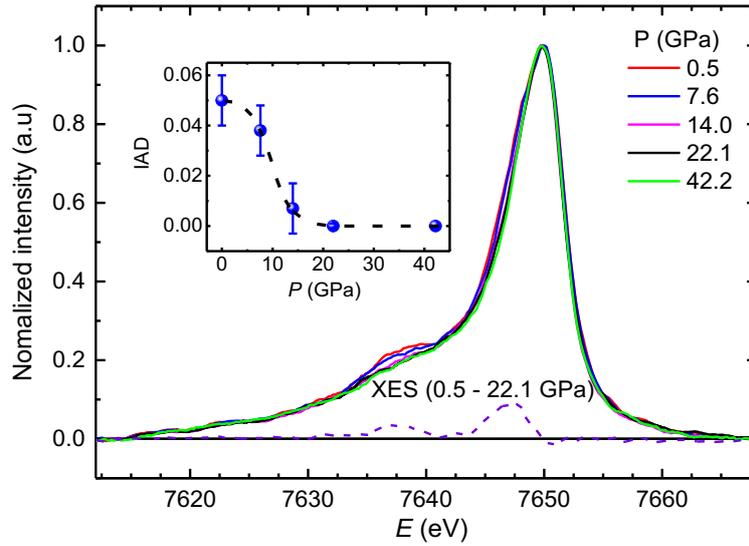


Figure 3. XES for Co- $K_{\beta}$  edge of  $\text{PbCoO}_3$  at different pressures and room temperature. The pre-edge peak decreases with increasing pressure up to 22.1 GPa, indicating a HS to LS transition of  $\text{Co}^{2+}$ . The inset shows the pressure dependence of IAD and the dash dot curve is guide for eyes.

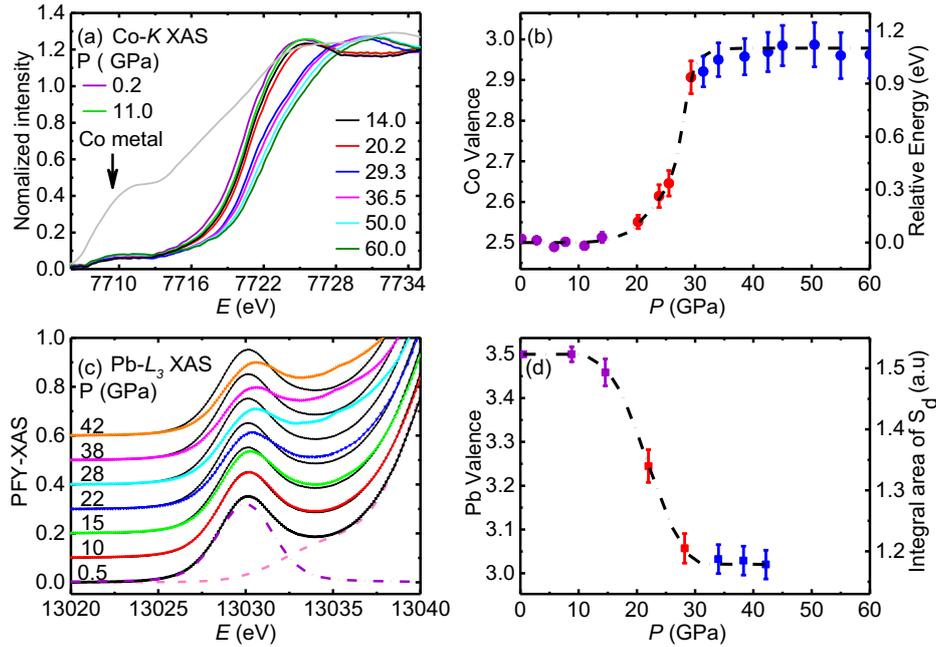


Figure 4. XAS of  $\text{PbCoO}_3$  measured at different pressures and room temperature. (a) The Co-K XAS spectra at some representative pressures. The XAS of Co metal as a reference at ambient pressure is also shown. (b) Relative energy shift of Co-K edge as a function of pressure at the normalized intensity  $\mu = 0.8$  after subtracting the background, and the valence state change of Co under pressure. The dot and dash curve is guide for eyes. (c) The pre-edge peak  $S_d$  in the Pb- $L_3$  XAS spectra measured using PFY mode at some representative pressures. For comparison, the XAS spectrum collected at 0.5 GPa is shown for the data taken at different pressures. The pink dash curve shows the background of PFY mode and the purple dot and dash curve shows the pre-edge peak  $S_d$  after subtracting the background. (d) The integral area of  $S_d$  and the valence state change of Pb as a function of pressure. The dot and dash curve is guide for eyes.

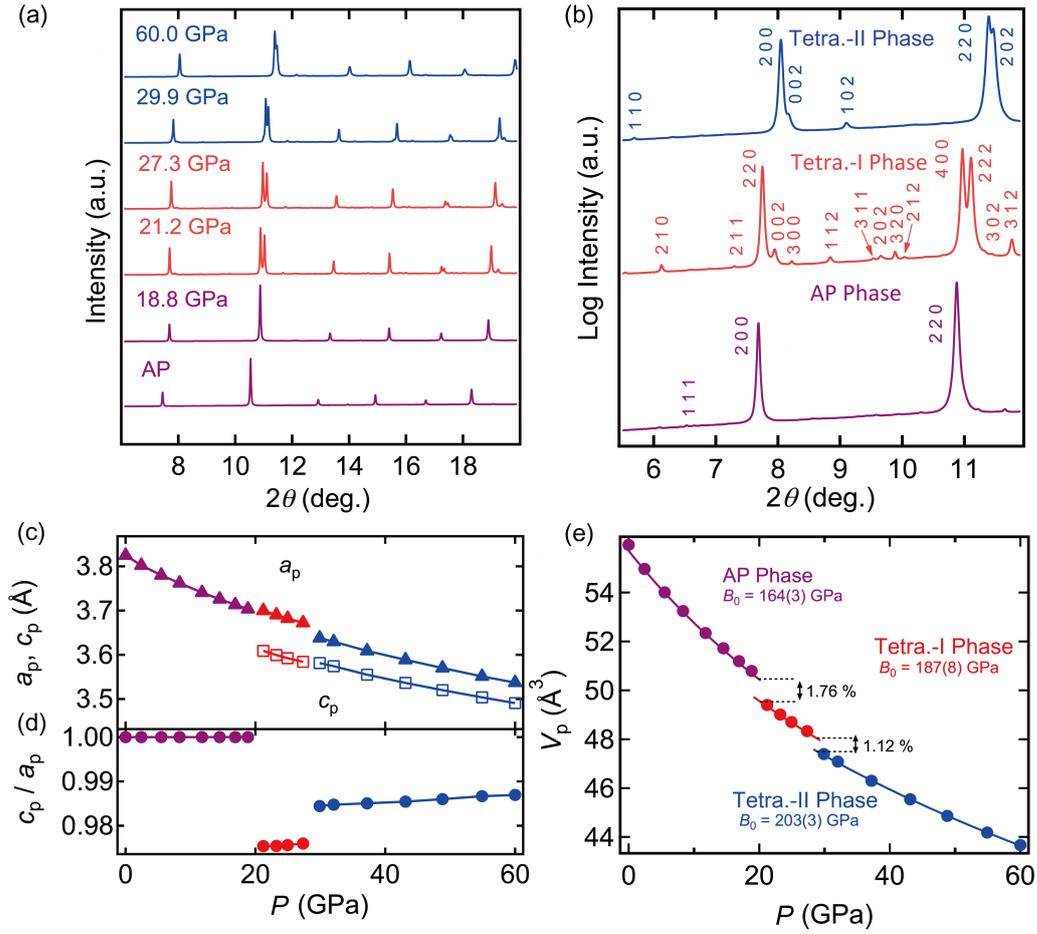


Figure 5. High-pressure SXR D patterns and related structural data. (a) Representative SXR D patterns collected at different pressures and room temperature. (b) SXR D patterns in log scale for the ambient pressure (AP) phase ( $P = 18.8$  GPa), Tetra.-I phase ( $P = 27.3$  GPa), and Tetra.-II phase ( $P = 60.0$  GPa). The peaks of AP, Tetra.-I and Tetra.-II phases are indexed with cubic  $2a_p \times 2a_p \times 2a_p$ , tetragonal  $2\sqrt{2}a_p \times 2\sqrt{2}a_p \times 2a_p$ , and tetragonal  $2a_p \times 2a_p \times 2a_p$  unit cells, respectively. Pressure dependence of (c) normalized lattice parameters, (d) the ratio of  $a/c$ , and (e) unit cell volume. The curves in (e) show the fitting results based on the Birch-Murnaghan equation of state as described in text.

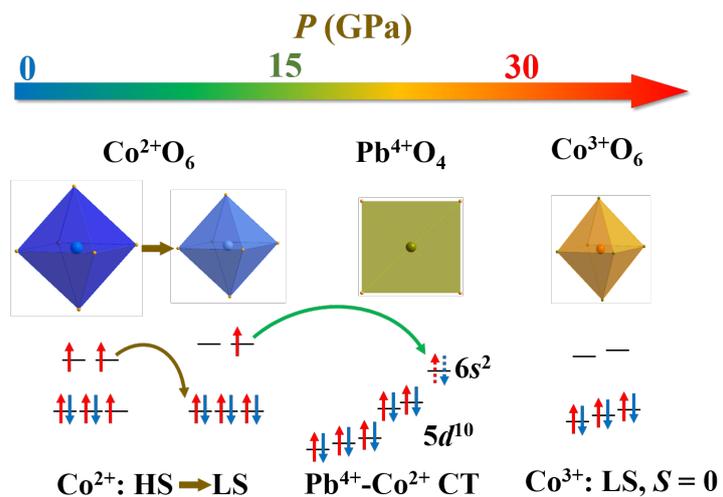


Figure 6. A schematic view for the origin of pressure induced spin state transition and charge transfer in  $\text{PbCoO}_3$ . The dot arrows in the  $6s^2$  orbitals of Pb show the transferred electrons from the LS  $\text{Co}^{2+}$ . CT = charge transfer.

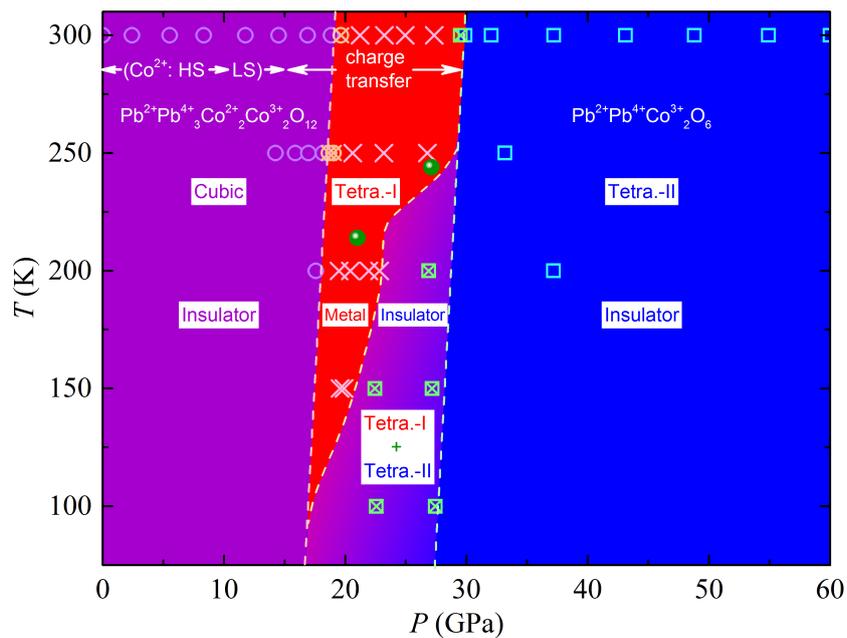


Figure 7. Pressure and temperature dependent phase diagram of  $\text{PbCoO}_3$ . The circle ( $\circ$ ), cross ( $\times$ ), and square ( $\square$ ) respectively stand for the cubic, Tetra.-I and Tetra.-II phases as determined from SXRD measurements. The dash curves approximately show the phase boundaries.

**For Table of Content (TOC) Only**

