



**HAL**  
open science

## Schottky barrier formation at the Fe/SrTiO<sub>3</sub> (001) interface: Influence of oxygen vacancies and layer oxidation

Rémi Arras, Julien Gosteau, Sylvain Tricot, Philippe Schieffer

► **To cite this version:**

Rémi Arras, Julien Gosteau, Sylvain Tricot, Philippe Schieffer. Schottky barrier formation at the Fe/SrTiO<sub>3</sub> (001) interface: Influence of oxygen vacancies and layer oxidation. *Physical Review B*, 2020, 102 (20), pp.205307. 10.1103/PhysRevB.102.205307 . hal-03100212

**HAL Id: hal-03100212**

**<https://hal.science/hal-03100212>**

Submitted on 26 May 2021

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Schottky barrier formation at the Fe/SrTiO<sub>3</sub>(001) interface: Influence of oxygen vacancies and layer oxidation

R. Arras\* and J. Gosteau

CEMES, Université de Toulouse, CNRS, UPS, 29 rue Jeanne Marvig, F-31055, Toulouse, France

S. Tricot and P. Schieffer

Univ. Rennes, CNRS, IPR (Institut de Physique de Rennes)–UMR 6251, F-35000 Rennes, France

Schottky barrier formation at metal/insulating oxide interfaces relies on complex mechanisms which are difficult to unravel. We propose a detailed numerical study of the atomic, magnetic and electronic properties of the Fe/SrTiO<sub>3</sub>(001) interface, in which we focused our discussion on different parameters which can affect the Schottky barrier height (SBH). The interface termination appears to be the most critical aspect to be controlled for this interface: While an ideal TiO<sub>2</sub>-terminated interface would guarantee a n-type barrier of about 1.2-1.6 eV, the presence of a SrO termination can drastically decrease its value down to few meV. The oxidation state of the interface is also an important criterium to maintain a high barrier value. Oxygen vacancies are always cited as the source of a deterioration of the SBH. For a TiO<sub>2</sub>-terminated interface, we found that in their most stable position, *i.e.* in the interface layer, the oxygen vacancies do not affect the value of the SBH; when moving some atomic layers away from the interface, the SBH on the contrary decreases regularly. We propose that oxidizing the interface would allow to improve the n-type SBH by healing the oxygen vacancies and forming an interfacial FeO layer, which seems favorable to the formation of a higher SBH.

## I. INTRODUCTION

The association of a metal and an insulator or semiconductor is at the heart of the formation of capacitors and Schottky diode, and then at the basis of many derived electronic devices such as dynamic random access memories (DRAM) or metal-oxide-semiconductor field-effect transistors (MOSFET).<sup>1,2</sup> A thorough study and understanding of their interface properties, and in particular of the interface oxidation state,<sup>3-6</sup> is thus crucial to use these heterostructures in more and more performant and demanding applications.

SrTiO<sub>3</sub> (STO) is a common oxide substrate with a cubic perovskite structure at room temperature, a lattice parameter of 3.905 Å and an experimental band gap of 3.2 eV. This material is ideal to perform the epitaxial growth of several kinds of multifunctional oxides having the same perovskite structure, but also of metallic compounds. The use of insulating oxides such as STO is particularly interesting for many devices because of its high electric permittivity. Providing a good control of its interface and a good choice of the metal, this oxide could allow to get Schottky barrier heights enabling to diminish the current leakage in miniaturized compounds. Among the main parameters to be controlled to optimize the interface properties, structural defects and in particular the oxygen vacancies (V<sub>O</sub>'s) are of the utmost importance;<sup>7-9</sup> they can especially participate to mechanisms turning the interface or some domains in the crystal to become metallic. For example, for more than 15 years now, STO has attracted lots of interest because of its ability to host a two-dimensional electron gas at its surface or interfaces.<sup>10-12</sup> If the origin of the two-dimensional electron gas is still debated, depending on the growth

condition and on possible post treatments, V<sub>O</sub>'s can play a crucial role in its emergence and its conduction properties;<sup>11,13-15</sup> the presence of V<sub>O</sub>'s is also one of the main hypothesis to explain the appearance of parent properties such as magnetism. Another important field of research which is currently driving lots of effort of research concerns the understanding of the resistive switching mechanisms when an electric field is applied, as they could be used to design future memories known as resistive random access memory (ReRAM). Such resistive switching has already been evidenced experimentally in metal/SrTiO<sub>3</sub> heterostructures and for these processes again the presence of V<sub>O</sub>'s is the main actor.<sup>16-18</sup>

In the formation of a Schottky barrier,<sup>19</sup> without considering the interaction (in terms of charge exchange or atomic relaxation) between the metal and the oxide layer, *i.e.* in the Schottky-Mott limit,<sup>20,21</sup> the band alignment is determined by the work function of the metal and the ionization potential of the oxide. The real Schottky barrier height (SBH) may be however mostly dependent of the so-called Fermi level pinning arising from two different mechanisms, an intrinsic contribution coming from the appearance of metal-induced gap states (MIGS) associated to the chemical bonding between the metal and the oxide and an extrinsic contribution which can originate from defects such as oxygen vacancies.<sup>19,22</sup>

Several studies have already been published on the growth of metallic layers on STO and the formation of Schottky barriers. The electronic and structural properties have also been addressed theoretically by the mean of first-principles calculations.<sup>22-24</sup> As for the previously discussed properties, for the SBH formation also the complex role of structural defects and in particular of oxygen vacancies may be expected to be crucial, but has however not been extensively studied numerically.

The numerous theoretical studies of oxygen vacancies in STO and near its surfaces show the complexity of such system.<sup>24–38</sup> Calculations of the  $V_O$  stabilities near STO surfaces have allowed to conclude that they are expected to be located close to the surface and preferably in  $TiO_2$  atomic layers, suggesting a possible migration of vacancies during the growth,<sup>24,36,38</sup> which could result in  $V_O$ -clusterization.<sup>39</sup> Thanks to nudged elastic band calculations, Brown, *et al.*,<sup>38</sup> found that the  $V_O$  diffusion is kinetically controlled and they calculated a diffusion barrier energy of 0.7 eV to move the  $V_O$  from the SrO subsurface layer to the  $TiO_2$  surface layer. For the surfaces again, Ma, *et al.*,<sup>24</sup> found that  $V_O$  can induce oxygen octahedra rotations (OOR), only when localized in a  $TiO_2$  atomic layer, which can help stabilize the defect in such atomic plane. They also extended their study to the Au/STO(001) interfaces, for which their results are qualitatively found to be the same. The n-type SBH at the Au/STO interface, defined as the difference between the conduction band minimum (CBM) energy and the Fermi level energy  $E_F$ , is calculated to be 1.0(0.6) eV for a SrO( $TiO_2$ ) termination. These values are strongly reduced to 0.2(0.1) eV when a  $V_O$  is introduced in the interface atomic layer and the STO layer can become conducting, forming an Ohmic-type contact, when the vacancy is located further from the interface.

Catrou, *et al.*<sup>8</sup> experimentally studied Fe/STO(001) interfaces. Their samples displayed mostly interfaces with a  $TiO_2$  termination, the SrO termination covering approximately 10 to 20 % of the surface area. The interface formation with the metallic electrode is made during the deposition of the first 10 monolayers (ML's) of Fe. Below this value, the CBM appears to be below the Fermi level, which corresponds to a metallization of STO, while above a thickness of 15 ML's, a SBH of  $0.05 \pm 0.07$  eV is stabilized. From current-voltage measurements, a SBH lower than 0.25 eV is estimated. These experimental results do not seem directly comparable with theoretical calculations performed on Cr/STO interfaces, which rather suggested SBH of 1.3 (1.0) eV for a  $TiO_2$  (SrO)-terminated interface.<sup>22</sup> The hypothesis that the SBH could be reduced due to the presence of oxygen vacancies in STO has been advanced by Catrou, *et al.* to explain such discrepancy, which we have tried to verify with the present study.

In the following we provide a theoretical insight of the SBH formation at the Fe/STO(001) interface. We will first give a as global as possible overview of the electronic structure, intimately linked with the variation of the magnetic properties at this interface, as a function of the atomic structure: Three different structural parameters will be envisioned, *i.e.* 1) the interface termination, 2) the presence of oxygen vacancies and 3) the potential oxidation of the Fe layer near the interface. Considering this set of parameters, we aim at understanding the lowering of the SBH measured experimentally at the Fe/STO(001) interface. All these results have been obtained by taking explicitly into account of the interfaces; a comparison

with bulk calculations and a discussion of the calculation parameters is given in the appendices, as well as a full description of the magnetic properties calculated in the presence of an oxygen vacancy.

## II. DETAILS OF THE CALCULATIONS

We performed first-principles calculations based on the density functional theory (DFT) using the Vienna *ab initio* Simulation Package (VASP)<sup>40,41</sup> with the projector augmented-wave method<sup>42</sup> and a cut-off energy of 500 eV. The generalized-gradient approximation proposed by Perdew, Burke and Ernzerhof and revised for solid (PBEsol) was used for the exchange-correlation functional.<sup>43</sup> A "+U" correction<sup>44</sup> was applied to the  $d$  electrons of Ti atoms, with a  $U_{\text{eff}}$  ( $= U - J$ ) value of 8.0 eV to improve the band-gap calculation and as proposed in Ref. 16 and 23: Using such parameter, we calculated a band gap around the Fermi level  $E_F$  of 2.83 eV, that is 1 eV higher than with the PBEsol approximation alone and closer to the experimental value of 3.2 eV. A comparison of the electronic properties of the bulk STO in the presence of oxygen vacancies is given in the Appendix A with a discussion of the influence of some calculation parameters, including the choice of  $U_{\text{eff}}$ .

The lattice parameter of bulk STO has been calculated to 3.950 Å with the PBEsol+U method, *i.e.* 1.15 % higher than the experimental value. The atom coordinates and lattice parameters have been optimized until all forces are below 5 meV/Å. For the interface calculations, a symmetric slab was used with a  $(2 \times 2)$  lateral dimension; in the appendix A, we also discuss the dimensionality effects linked to the limited size of our supercells. The lattice parameter was fixed to the bulk equilibrium value corresponding to the chosen approximation for the exchange-correlation functional. The slab thickness in the [001] direction was of 10.5 unit cells of STO (that is 21 atomic ML's), with two  $TiO_2$  or SrO-terminated interfaces, each one associated to a 5-ML's-thick Fe layer. Fe atoms located at the interface are placed on top of the oxygen atoms for the  $TiO_2$  termination, which has been found to be the most stable configuration for many metal/perovskite systems;<sup>45–47</sup> they are located on top of oxygen and Sr atoms for the SrO interface. Each Fe surface is separated by at least 15 Å of vacuum.

Finally, the first Brillouin zone was sampled with a  $8 \times 8 \times 1$  Monkhorst-Pack grid<sup>48</sup> for the structural optimization and the electronic structure is then calculated with a slightly denser mesh of  $10 \times 10 \times 1$ . The SBH are calculated using the layer-resolved densities of states (LDOS).<sup>24,49,50</sup> More details about the calculation of the SBH are given in the Appendix B.

### III. GENERAL PROPERTIES OF THE Fe/SrTiO<sub>3</sub>(001) INTERFACES

#### A. Dependence on the interface termination

We first analyze the properties of perfect Fe/STO interfaces with a TiO<sub>2</sub> or SrO termination.

We define the cleavage or separation energy  $E_{\text{sep}}$  as the energy difference per surface area  $A$  between the ground state total energy of the heterostructure  $E_{\text{HS}}$  and the sum of the ground state energies of the two relaxed Fe and STO layers taken separately and respectively denoted as  $E_{\text{layer}}^{\text{Fe}}$  and  $E_{\text{layer}}^{\text{STO}}$ .

$$E_{\text{sep}} = \frac{1}{2A} [E_{\text{HS}} - (E_{\text{layer}}^{\text{Fe}} + E_{\text{layer}}^{\text{STO}})] \quad (1)$$

We calculated that this separation energy is  $E_{\text{sep}} = -7.34 \text{ eV nm}^{-2}$  and  $E_{\text{sep}} = -5.84 \text{ eV nm}^{-2}$ , respectively for a TiO<sub>2</sub> and a SrO termination, suggesting that the former is indeed more stable.

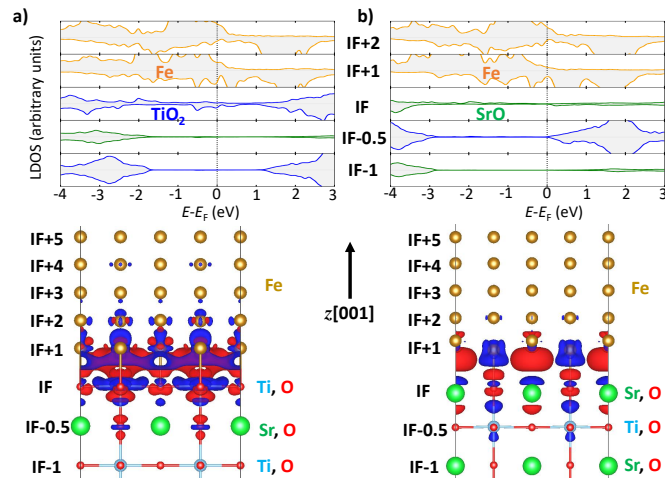


FIG. 1. (top) Layer-resolved densities of states (LDOS) of the (001) atomic planes and (bottom) charge density difference near the a) TiO<sub>2</sub>- and b) SrO-terminated interfaces (IF). The charge density difference is defined by the formula  $\Delta\rho = \rho_{\text{HS}} - (\rho_{\text{STO}} + \rho_{\text{Fe}})$ , where  $\rho_{\text{HS}}$ ,  $\rho_{\text{STO}}$  and  $\rho_{\text{Fe}}$  are respectively the charge densities for the heterostructure, the STO and the Fe layers. Red area corresponds to a positive  $\Delta\rho$ , while blue area is for negative values.

The presence of the interface induces low structural distortions. The calculated Fe-O distances are 1.914(1.983) Å at the TiO<sub>2</sub>(SrO)-terminated interface and the Ti-O bond lengths near the interfaces are only increased by 0.5 % in comparison to the bulk value. Our calculated Fe-O distance at the interface is in agreement with previously reported value of 1.961 Å.<sup>51</sup> The oxygenation buckling, defined as  $\Delta z = z(\text{cation}) - z(\text{O})$  with  $z$  the coordinate along the [001] direction, is a quantity which can be related to the emergence of a local electric

polarization. A slight buckling of  $\Delta z = 4 \times 10^{-2}$  Å is observed in the interface layer with the TiO<sub>2</sub> termination, and of  $\Delta z = 2.5 \times 10^{-1}$  Å for the SrO interface. Still for the SrO-terminated interface, this same buckling is of  $3 \times 10^{-2}$  Å in the sub-interface TiO<sub>2</sub> layer, while it rapidly tends to 0 Å for the TiO<sub>2</sub>-terminated interface. Finally, when looking in more details the atomic structure near the interface [see the bottom of Fig. 1b], it is also interesting to notice that the SrO termination induces more distortions in the first Fe atomic layer near the interface (denoted IF+1), which can be easily explained by considering the two different atomic sites of this layer, half of the atoms being bonded to oxygen atoms and consequently attracted toward the STO layer, the other half of the interface Fe atoms being on top of a Sr atom, and then repelled from the interface.

The calculated electronic structure at the Fe/STO interface is in agreement with previous report from the literature<sup>51</sup> and shares different similarities with parent interfaces between a Fe or Co electrode and a ferroelectric perovskite with a TiO<sub>2</sub> surface termination.<sup>52-54</sup> The bottom of the conduction band in STO has mostly a Ti-d character. Because the d bands of Fe atoms are more than half occupied, most of the transferred electrons have a minority spin momentum. The LDOSs of the Fig. 1a show indeed the appearance of minority-spin Ti-d<sub>xz,yz</sub> states in the band gap, just around the Fermi level and well localized at the interface, which has for consequence to induce a negative spin magnetic moment of  $-0.32 \mu_{\text{B}}$  on the Ti atom. This induced spin magnetic moment on the Ti atoms goes in hand with an increase of the spin magnetic moment of the interfacial Fe atoms, from an averaged value of  $2.12 \mu_{\text{B}}$  in the center of the layer up to  $2.31 \mu_{\text{B}}$  at the interface. For the SrO interface, on the contrary, we do not observe any clear MIGS in the STO band gap near the interface (Fig. 1b). We calculated low induced magnetic moments on the oxygen and Ti first-neighbors of the interface, of approximated values of  $0.05 \mu_{\text{B}}$ , and almost no variation of the spin magnetic moment for the Fe atoms on top of the hollow atomic site; on the contrary, the Fe atoms bonded to the oxygen atoms at the interface undergo a high increase of their magnetic moment to  $2.91 \mu_{\text{B}}$ , which is  $0.13 \mu_{\text{B}}$  higher than the magnetic moment of the Fe atoms at the bare surface and  $0.79 \mu_{\text{B}}$  higher than the bulk value. Finally, as it will be discussed later, we calculated the formation of an internal electric field of approximately  $-0.01 \text{ V Å}^{-1}$  for the TiO<sub>2</sub>-terminated interface, which can result from the charge transfer at the interface, while it is almost null for the SrO termination.

Another way to tackle the charge transfer through the interface is by performing the Bader charge analysis.<sup>55-57</sup> The formal electric charge carried by the Ti cation in STO is +4e, by approximating this compound to a ionic cristal. We calculated a Bader charge of +2.33 e for the Ti atoms in the bulk compound. The calculated value in the center of our supercell is similar (+2.25 e), but it decreases to +2.10 e near the TiO<sub>2</sub> interface, indicating

an increase of the number of electrons, while no change is noticed for the SrO interface. The charge transfer, due to the proximity between the Ti and Fe atoms at the  $\text{TiO}_2$  interface, can be noticed in the charge density difference (CDD) plotted in Fig 1a, *i.e.* the charge difference between the complete heterostructure, and the sum of the charge densities of the two Fe and STO layers with the same atomic structure. We can see on this figure that we have large positive red areas above the interfacial Ti atoms, with a clear out-of-plane component, which is consistent with the populating of the  $d_{xz,yz}$  bands. The establishment of the chemical bonds between Fe and oxygen atoms may be also noticed due to the charge transfer from the negative blue areas with a  $d_{z^2}$ -orbital shape and located on the Fe atoms to the red areas with  $p_z$ -orbital shapes located on the oxygen atoms in the interfacial  $\text{TiO}_2$  atomic layer. In the case of the SrO termination (Fig. 1b), most of the charge transfer occurs from the Fe atoms linked to one oxygen anion to this same oxygen anion, which is highlighted by the spin polarization of out-of-plane orbitals. We can in particular notice alternating negative and positive CDD in the (001) plane of the interface, which can directly be related to the structural distortion: Negative CDD is associated to Fe atoms bonded to oxygen atoms with which they experience a charge transfer, while the positive CDD can be seen in the interstitial zone below the Fe atoms which are repelled from the interface.

### B. Effect of the oxygen vacancies

We will now discuss the effect of the presence of one  $V_O$  as a function of its location with respect to the interface. We will mostly focus our discussion on the case of the most stable  $\text{TiO}_2$ -terminated interface.

*a. Formation energy:* The Fig. 2 displays the formation energy<sup>58,59</sup>  $E_d$  of one oxygen vacancy as a function of its position in the successive (001) atomic layers and calculated following the formula:

$$E_d = \frac{1}{2} [E_{\text{HS}+nV_O} - E_{\text{HS}} - n(\mu_{\text{O}_2} + \Delta\mu_{\text{O}_2})] \quad (2)$$

with  $E_{\text{HS}+nV_O}$  and  $E_{\text{HS}}$  respectively the ground state energy of the heterostructures with and without oxygen vacancies  $V_O$  and which are formed by two equivalent interfaces.  $\mu_{\text{O}_2}$  is the chemical potential of a  $\text{O}_2$  molecule and  $n$  corresponds to the number of oxygen vacancies. Because we will only be interested in studying the variation of formation energy as a function of the position of the vacancies and for the sake of simplicity, we neglected the term  $\Delta\mu_{\text{O}_2}$ , which depends on the growth conditions and we only considered the formation of electrically-neutral oxygen vacancies. Some results considering charged  $V_O$  are described in the Appendix A.

As calculated by Ma, *et al.* for a Au/STO(001) interface,<sup>24</sup> we found that the position of the oxygen vacancy

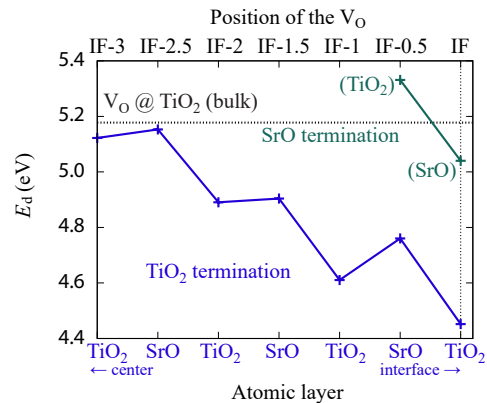


FIG. 2. The formation energy of the oxygen vacancy as a function of its position according to the interface for the  $\text{TiO}_2$ -terminated (blue) and SrO-terminated interface (green). The black dotted line corresponds to the formation energy (5.18 eV) of a  $V_O$  calculated in a  $2 \times 2 \times 5$  bulk supercell and the  $V_O$  located in a  $\text{TiO}_2$  (001) atomic layer. When the  $V_O$  is located in a SrO layer, the formation energy increases up to 5.68 eV.

is more stable when the vacancy is located near the interface and in a  $\text{TiO}_2$  layer: The formation energy increases by 0.2-0.3 eV from the first to the second atomic ML away from the interface, and by approximately 0.8 eV further. Oxygen vacancies having a lower formation energy near interfaces has already been predicted in several metal/oxide systems and may be partly attributed to the presence of the partially-occupied MIGS's which allow to accommodate the excess of electrons released by the  $V_O$  (see Ref. 60 and references therein). As discussed later, the atomic structure near the interface can undergo different kind of structural distortions (OOR or buckling), depending on the position of the  $V_O$ ; in addition to the symmetric slab with limited thickness which was used, this makes difficult any comparison between the calculated formation energies of the  $V_O$  in the slab and in the bulk compound.

We extended the previous calculations to the formation energy  $E_d$  of two  $V_O$ 's as a function of the distance separating them. Because we found that the interfacial  $\text{TiO}_2$  layer (IF) is the most suitable position for the formation of a  $V_O$ , we considered that one of the two vacancies is necessarily in this layer. We can easily see from the Table I that the 2  $V_O$ 's present a clear tendency to clusterize, with the lowest formation energy  $E_d = 4.17$  eV, calculated when the two  $V_O$ 's are both in the IF layer and at the minimum distance of  $a/\sqrt{2}$ , *i.e.* 0.28 eV/ $V_O$  lower than the formation energy calculated with only one  $V_O$ . Using a  $3 \times 3 \times 4$  supercell, Jeschke, *et al.* also found that a tendency of the  $V_O$ 's to clusterize in the perpendicular direction near a  $\text{TiO}_2$ -terminated surface, while they found on the contrary that the  $V_O$ 's tend to be homogeneously separated when located inside the same parallel surface layer.<sup>39</sup>

Layer 1	Layer 2	$d(V_O - V_O)$	$E_d$ (eV/ $V_O$ )
IF	IF	$\simeq a/\sqrt{2}$	4.17
IF	IF	$\simeq a$	4.24
IF	IF	$\simeq 2a$	4.45
IF	IF-0.5	$a/\sqrt{2}$	4.46
IF	IF-0.5	$\simeq \sqrt{3}a/2$	4.57
IF	IF-1	$\simeq a$	4.54

TABLE I. . Formation energies  $E_d$  calculated using the Eq. 2. The energies are given as a function of the position of 2 oxygen vacancies, which are located respectively in the atomic layer 1 and layer 2. The label IF corresponds to the  $TiO_2$  terminated interface, as defined in Fig. 1a. The distances between the two oxygen vacancies  $V_O$  are given as a function of an approximated cubic lattice parameter  $a$  (which is fixed to the bulk value for in-plane directions and may vary for out-of-plane directions). The case of two  $V_O$  located at the interface and at a distance of  $\simeq 2a$  is strictly equivalent to the previously discussed case with 1  $V_O$  in the  $2 \times 2$  lateral supercell.

*b. Atomic structure relaxation:* After optimization of the atomic structure, we found that the averaged inter-plane distance in STO is reduced by 3.8 % in the vicinity of the perfect interface compared to the bulk equilibrium value. This inter-plane distance increases to recover the bulk value from 3 ML's away of the interface. Including an oxygen vacancy will add some distortions, inducing oscillations of these inter-plane distances. As shown in Fig. 3a, this change of out-of-plane lattice parameter is accompanied by a cation-oxygen buckling between the interface and the atomic plane which contains the oxygen vacancy: This buckling  $\Delta z$  is characterized by a positive variation of the  $z[001]$  coordinate of approximately  $0.13 \text{ \AA}$ , which is approximately of the same magnitude that can be calculated for the ferroelectric bulk oxide  $BaTiO_3$ .

In addition to the cation-oxygen buckling, when the oxygen vacancy is located in a  $TiO_2$  plane, we can notice the appearance of OOR's in the planes located after the  $TiO_2$  vacancy plane, toward the center of the slab (see Fig 3b). As it is discussed in the appendix A, the presence of OOR is also noticed in the bulk compound<sup>35</sup> due to the symmetry reduction induced by the  $V_O$  and we can expect that such distortions help to reduce the formation energy of the defects, explaining why  $TiO_2$  atomic layers are an energetically more favorable location for a  $V_O$  than SrO layers, as proposed by Ma, *et al.* in the case of  $SrTiO_3$  surfaces.<sup>24</sup> When analyzing the Fig. 2, we can see in particular that the energy-formation difference between a  $TiO_2$  or a SrO location decreases as we are moving far away from the interface. Such observation may be directly linked to the proximity to the interface, but can also be a result of the finite size of our slab and the special symmetrical geometry we chose to use: When we move the two symmetric images of oxygen vacancies toward the center of the slab, we reduce

the number of atomic planes which can host the OOR. This potential calculation artifact, with the appearance of cation-oxygen buckling, explain why moving the  $V_O$  toward the center of the slab does not allow to recover the two formation energies (depending on which layer is hosting the  $V_O$ ), different by 0.5 eV for a  $2 \times 2 \times 5$  bulk supercell (see appendix A and Fig. 2).

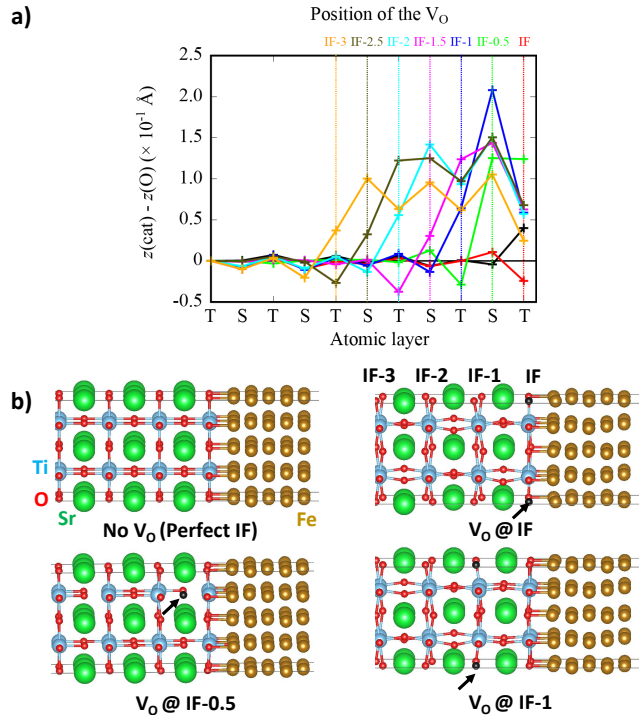


FIG. 3. a) Cation-oxygen buckling; the black curve corresponds to the reference structure without  $V_O$ . The letters "T" and "S" represent respectively the  $TiO_2$  and SrO atomic layers. b) Atomic structure of the Fe/SrTiO<sub>3</sub> without any oxygen vacancy  $V_O$  and with one oxygen vacancy in three different positions.

*c. Electronic structure:* Associated with the atomic distortions and the cation-oxygen buckling  $\Delta z$ , we have the creation of electric dipoles and it is possible to calculate a local electric polarization  $P_i$  by using Born effective charges  $Z^*$ :

$$P_i^l = \frac{e}{\Omega} \sum_{\kappa} Z_{z,i,\kappa}^* (\delta z)_{i,\kappa} \quad (3a)$$

$$P_i = P_i^l + \frac{1}{2} (P_{i-0.5}^l + P_{i+0.5}^l) \quad (3b)$$

with  $P_i^l$  the contribution to the electric polarization along  $z[001]$  of the atomic layer  $i$  and calculated by summing the Born effective charges  $Z_{z,i,\kappa}^*$  of the  $\kappa$  atoms forming the layer, multiplied by the variation of the coordinate  $z$  according to the middle between the averaged position of the adjacent layers:  $(\delta z)_{i,\kappa} = \langle z \rangle_{i,\kappa} - \frac{\langle z \rangle_{i-0.5} + \langle z \rangle_{i+0.5}}{2}$ . The volume of the unit cell  $\Omega$  is also

expressed as the volume delimited by these two adjacent layers, which yields to  $\Omega = a^2|\langle z \rangle_{i+0.5} - \langle z \rangle_{i-0.5}|$ . In the Fig. 4a, we consider an in-plane-averaged electric polarization  $P_i$ , which follows the expression of Eq. 3b and which shares some similarities with the equation proposed in Ref. 50. The Born effective charges calculated for the bulk STO compound are  $Z_{z,Ti}^* = 5.93$  e,  $Z_{z,Sr}^* = 2.55$  e,  $Z_{z,O\parallel}^* = -1.88$  e and  $Z_{z,O\perp}^* = -4.75$  e, respectively for the Ti, Sr, in-plane oxygen and out-of-plane oxygen atoms. We can see that we obtain an almost constant electric polarization from the atomic layer where the  $V_O$  is located and pointing toward the interface. The value of this polarization  $P_i$  decreases almost regularly between 35 and 19  $\mu\text{C cm}^{-2}$ , when moving the  $V_O$  from the  $\text{TiO}_2(\text{IF-1})$  to the  $\text{TiO}_2(\text{IF-3})$  atomic layer. The  $V_O$  in the interface plane (IF) appears to be a particular case for which the charge transfers induce locally a reversal of the polarization sign.

The Fig. 4b is complementary to the calculated local electric polarization. It presents the 1s core energy levels of the oxygen atoms compared to their calculated bulk value:  $\Delta E_{1s} = E_{1s}^i - E_{1s}^{\text{bulk}}$ . The relative energy of the core levels is shifted between each atomic layer  $i$  when going away from the perfect  $\text{TiO}_2$ -terminated interface (black curve), which corresponds to a band bending and is a consequence of the appearance of an internal electric field, oriented toward the center of the slab and evaluated to  $E_{\text{field}} = \frac{\delta(\Delta E_{1s})}{e\delta z} \sim -0.01$  V  $\text{\AA}^{-1}$ . The presence of the  $V_O$  at the interface reduces the value of this electric field, while a net positive electric field is created when the  $V_O$  is located in the next layers, with a value of approximately  $+0.045$  V  $\text{\AA}^{-1}$ , when in the  $\text{TiO}_2(\text{IF-3})$  layer. This estimated value of the electric field would correspond to an averaged value of electric polarization of  $P = \epsilon_r \epsilon_0 E_{\text{field}} \sim 16$   $\mu\text{C cm}^{-2}$  (considering a calculated relative permittivity of  $\epsilon_r = 39.4$ ), *i.e.* a value close to the previous estimation of  $P_i$ . It is also interesting to note that the formation of this internal electric field may partly explain why the neutral oxygen vacancies have a higher formation energy far from the interface, because this field will add an electrostatic contribution to the total energy equal to  $ezE_{\text{field}}$ , as discussed in the Ref. 61. If this assumption is correct, we can emit the hypothesis that the formation of positively charged  $V_O$ , which we only calculated for the bulk oxide (see Appendix A), could maybe be more favorable away from the interface, in order to reduce the amount of localized charges.

The variations of the spin magnetic properties described in the Appendix C are witnesses of the structural and electronic modifications arising from the presence of the  $V_O$ , and thanks to their study, it is possible to obtain a guess of the charges localized near the  $V_O$  or transferred to the interface. From our calculations, we have found that when the  $V_O$  is in the  $\text{TiO}_2$  interface layer, the partially-occupied MIGS's trap the 2 electrons released by the neutral vacancy (*i.e.* 0.5 electron/Ti atom). When the  $V_O$  is located in atomic layers further away from the interface, only a part of the released

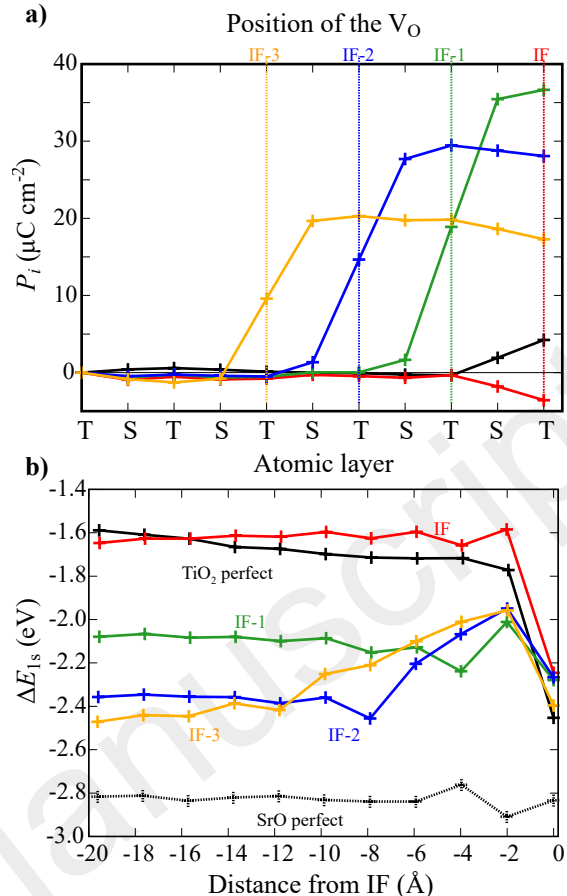


FIG. 4. a) Local electric polarization  $P_i$  as a function of the position of the  $V_O$  and of the atomic layer  $i$  (T is for  $\text{TiO}_2$  and S for SrO) and b) variation of the O-1s energy level as a function of the distance to the interface. The value  $\Delta E_{1s}$  is given according to the energy level calculated for the bulk STO.

charges stays localized in the  $\text{TiO}_2$  layer first-neighbor of the vacancy, the other part being transferred to the  $\text{TiO}_2$  interface layer as a result of the electric polarization. The further the  $V_O$  from the interface is, the lower the amount of transferred charges; which is consistent with the decrease of the averaged absolute value of the spin magnetic moment of the interfacial Ti atoms. Taking again the example of the oxygen vacancies located in the  $\text{TiO}_2(\text{IF-3})$  atomic layer, we can from the calculated spin magnetic moment consider that this  $\text{TiO}_2(\text{IF-3})$  layer is charged with  $Q_{V_O} = -1.06$  e, while the  $\text{TiO}_2(\text{IF})$  layer possess an excess of  $Q_{\text{IF}} = -2.15$  e. With the model of a plane capacitor and doing the approximation that the charges are uniformly spread in the atomic layers, we obtain the Eq. 4:

$$E_{\text{field}} = \frac{Q_{V_O} - Q_{\text{IF}}}{2\epsilon_r \epsilon_0 A} \quad (4)$$

and we can calculate that these charges would lead to the creation of an internal electric field of  $E_{\text{field}} =$

+0.040 V Å<sup>-1</sup>, which is consistent with the previous estimation obtained by fitting the variation of the core state energy.

### C. Effect of the Fe-layer oxidation

During the growth of the Fe layer, the formation of oxygen vacancies in STO can be the result of the migration of oxygen atoms toward the interface, partially oxidizing the metal layer<sup>12,62</sup>, in our case the Fe layer. The formation of an FeO(IF+1) oxide at the TiO<sub>2</sub>-terminated interface can also be controlled by growing the layer in an oxygen-rich atmosphere. We considered here the simple structure for which the atomic Fe layer at the interface is fully oxidized, forming a two-dimensional FeO layer in between Fe and STO; the added oxygen atoms are located such that they form a two-dimensional face-centered square lattice with the Fe atoms (see Fig. 5a).

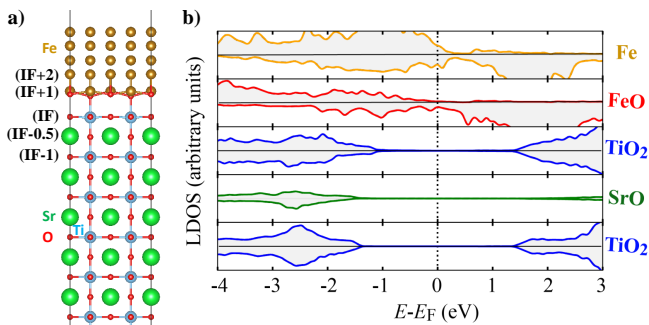


FIG. 5. a) Atomic structure of the oxidized TiO<sub>2</sub>-terminated Fe/SrTiO<sub>3</sub> interface and b) the corresponding LDOS of the interfacial layers. The calculations have been performed with a  $U_{\text{eff}}$ -dependent correction applied to the 3d bands of Fe atoms.

Our calculations show that the magnetic coupling in the FeO layer is ferromagnetic, with an energy difference of -0.17 eV/formula unit (f.u.) of FeO (-0.22 eV/f.u. if we add a  $U$ -dependent correction with  $U_{\text{eff}}(\text{Fe}, 3d) = 4$  eV). The oxidation is accompanied by a large increase of the Fe spin magnetic moment to 3.08  $\mu_B$  and the induction of a magnetic moment of 0.18  $\mu_B$  on the oxygen atoms of the same layer. On the contrary, the Ti and O atoms of the interfacial TiO<sub>2</sub> layer only display spin magnetic moments lower than 0.05  $\mu_B$ , which suggests a lower interaction between these atoms and the Fe layer. This statement is consistent with the larger Fe-O interatomic distance (2.459 Å) calculated for this oxidized interface, and which results in the quasi-disappearance of the gap states in the LDOS (as shown in Fig. 5b), in accordance with the calculated electronic structure reported at the oxidized Co/Pb(Zr,Ti)O<sub>3</sub> interface.<sup>54</sup>

## IV. SCHOTTKY BARRIER FORMATION

Having discussed the main properties of the Fe/STO interfaces, we can now address the problematic of the SBH formation.

We calculated a work function of 4.01 eV for the Fe layer (the experimental value is approximately 4.67-4.81 eV<sup>63</sup>). By using the calculation methods described in Ref. 22, we also obtained an ionization potentials of 5.30 eV and 3.78 eV for the relaxed STO surfaces, with respectively a TiO<sub>2</sub> or SrO termination. According to the Schottky-Mott rule, *i.e.* without considering the band alignment and the interface atomic structure relaxations, we would expect the Fermi level of the Fe to be located close to the middle of the band gap of STO for a perfect TiO<sub>2</sub>-terminated interface, giving a p-type SBH of 1.29 eV, while it should be below the valence band maximum for the other termination, then creating an Ohmic contact. However, calculating directly the SBH by using the LDOS provides a somewhat different scenario for the second interface: We calculated a p-type SBH of 1.61 eV and a n-type value of 1.23 eV (1.59 eV if we consider the experimental band gap of 3.2 eV) for the TiO<sub>2</sub>-terminated interface; for the SrO interface, the calculated p-type SBH is almost equal to the calculated band gap energy, *i.e.* 2.80 eV and we then found a almost null, but not vanishing, n-type SBH of 10 meV ( $\approx 0.4$  eV with the experimental band gap). The reported presence of 10-20 % of SrO termination could thus possibly corroborate the large reduction of the n-type SBH measured experimentally ( $0.05 \pm 0.07$  eV).<sup>8</sup> For this last interface, the bonding between the two layers at the interface and the relaxation of the atomic structure are critical to obtain the Schottky behavior. Calculating the ionization potential for a STO layer with the atomic structure of the interface, we indeed obtain an increase of 0.5 eV of its value, compared with the relaxed SrO surface.

From a more technical point of view and still for the SrO-terminated interface, we should mention that, on the contrary to the TiO<sub>2</sub>-terminated interface, the calculation of the p-SBH is also strongly dependent on the  $U_{\text{eff}}$  parameter used for the calculation: Increasing the  $U_{\text{eff}}$  value from 0 to 8 eV lowers the occupied valence states regarding to the Fermi energy and thus increases the p-SBH by approximately 0.8 eV. Qualitatively, the SrO-terminated interface displays lower n-SBH (by 0.5 to 1.5 eV) than the TiO<sub>2</sub>-terminated one, which is consistent with the calculations displayed in Ref. 22 for the Cr/STO interface. For the interface between the noble metal Au and STO, an opposite behavior has been calculated with a n-type SBH higher for the SrO interface (1.0 eV) than for the TiO<sub>2</sub> termination (0.6 eV).<sup>24</sup>

When a V<sub>O</sub> is introduced in the structure and is located in the TiO<sub>2</sub> interface layer, the SBH is unaffected if compared to the non-defective interface because the modifications of the electronic structure remain mostly localized at the interface. When the vacancy is moved toward the center of the slab, we have a decrease of the



n-type SBH: This decrease is drastic, by 0.7 eV, from the interface (IF) to the first-neighbor monolayer (IF-0.5), before following a quasi-linear variation between the atomic layers IF-1 and IF-3, where it reaches a value of 0.38 eV.

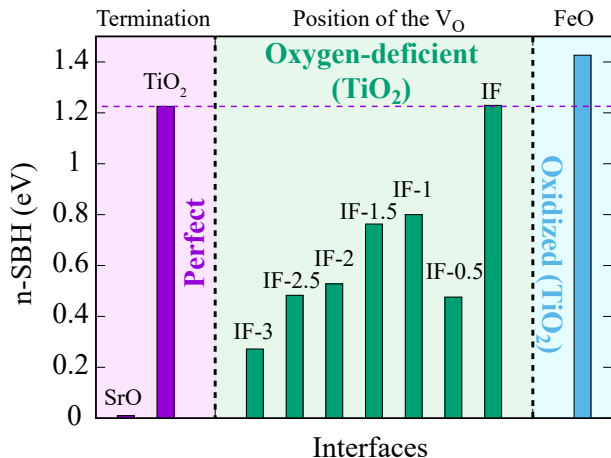


FIG. 6. Summary of the different n-type Schottky barrier heights (SBH) calculated for the perfect SrO- and TiO<sub>2</sub>-terminated interfaces (left) and for the TiO<sub>2</sub>-terminated interface with an oxygen vacancy (center) or an oxidized FeO layer (right).

If we consider now the SrO interface termination for which the SBH is already strongly reduced without any defects, the presence of a  $V_O$  in the SrO interfacial layer slightly increases the calculated n-SBH from 10 meV to 75 meV, while the  $V_O$  in the TiO<sub>2</sub> sub-interface layer induces some band crossing of the Fermi level for TiO<sub>2</sub> atomic layers in the center of the slab, which indicates that the  $V_O$  combined with such interface termination are more likely to induce an Ohmic behavior.

As shown in the right part of Fig. 6, we calculated a higher n-type SBH, of 1.39 eV, when the first Fe layer is fully oxidized and the interface termination is FeO/TiO<sub>2</sub>. This value was obtained by applying a  $U_{\text{eff}}$ -correction of 4 eV on the d orbitals of the Fe atoms from the FeO layer; without this correction, a very close value of 1.47 eV was found, which indicates that this correction does not change significantly the result. Such result is important as it would suggest that both healing the oxygen vacancies and oxidizing the interface could contribute to an increase of the n-type SBH.

## V. CONCLUSION

We performed first-principles calculations based on the DFT+ $U$  to investigate different configurations of Fe/STO interfaces and to try to define which are the key parameters which would explain the measured low n-type SBH. Our results have been discussed regarding

the choice of the different computational parameters and their limitation.

We firstly found that the termination of a perfect interface (either Fe/TiO<sub>2</sub> or Fe/SrO) appears to be the most detrimental factor to get high n-type SBH and the most plausible scenario to explain the experimental measurements of the Ref. 8, the SrO termination leading to an almost zero barrier. According to our calculations, such termination, if combined with some additional defect like oxygen vacancies, would inevitably induce an ohmic behavior.

Providing that a TiO<sub>2</sub> termination is stabilized, oxygen vacancies may also induce some modifications of the SBH, but these modifications are expected to be more limited. We indeed found that, as in the case of the Au/STO interface,<sup>24</sup> the creation of a neutral  $V_O$  is energetically more favorable in the TiO<sub>2</sub> interface layer, where the partially occupied gap states, resulting from the chemical bonding with the Fe layer, can help to accommodate the charges released by the defect. If the formation or migration of  $V_O$  is still possible in atomic layers away from this interface layer, these locations are energetically less favorable; in that case, a part of the charges given by the  $V_O$  can stay localized on Ti atoms near the defect position and in addition distort the lattice and reduce the n-type SBH.

Healing the oxygen vacancies by heating post treatment or by growing the samples under an oxygen-rich environment would then help to preserve higher n-type SBH. In addition, we have found that oxidizing the first Fe layer near the interface would improve this value.

The control of the Fe/SrTiO<sub>3</sub>(001) interface would thus provide interesting opportunity to design magnetic Schottky junctions with tunable barrier heights and which could be coupled with innovative systems, like multiferroics with a magnetoelectric coupling controllable *via* the  $V_O$ 's or surfaces/interfaces hosting a (spin-polarized) two-dimensional electron gas.

## ACKNOWLEDGMENTS

This work was granted access to the HPC resources of CALMIP supercomputing center under the allocation 2019 and 2020-p19004.

## Appendix A: Bulk calculations

For comparison purposes with the interface properties, we propose in this appendix to describe the calculated bulk physical properties. This discussion is also the opportunity to address the question of the effect of the choice of  $U_{\text{eff}}$ . Bulk properties such as atomic distortions, formation energies or electronic properties can vary significantly as a function of the considered initial structure and the choice of the exchange-correlation approximation. It was for example shown that there is normally a

necessity to use large supercells (larger than  $3 \times 3 \times 3$ ) to avoid too strong interaction between the periodic images of the vacancy, and that the formation energy can vary by more than 1 eV between a cell of 40 atoms and one of 320 atoms,<sup>26,28</sup> while some studies reported a low variation of only 0.1 eV between a  $2 \times 2 \times 2$  and  $3 \times 3 \times 3$  supercell. If early studies have confirmed the presence of gap states using DFT+ $U$  or hybrid functionals,<sup>25,29,30,32,34</sup> Choi, *et al.* have suggested that such states disappear when using sufficiently large supercells (625-1080 atoms) with a cubic structure.<sup>35</sup> The same authors also proposed that a local antiferrodistortive-like structure could be induced by oxygen vacancies, with some associated gap states.

*a. Effect of the supercell geometry and size:* Our first bulk calculations were performed with the PBEsol+ $U$  approximation and using a  $2 \times 2 \times 2$  and  $3 \times 3 \times 3$  supercells. With  $U_{\text{eff}} = 8$  eV, we respectively found a formation energy of 5.95 eV and 5.50 eV. For a comparison with the experience, Catrou, *et al.*<sup>8</sup> estimated from photoemission analysis a surface density of vacancies of  $\simeq 2 \times 10^{14}$  cm<sup>-2</sup>, *i.e.* 1 % of vacancies ; removing an oxygen atom from a  $2 \times 2 \times 1$  supercell corresponds instead to 8.3 % of vacancies, and 3.7 % for a  $3 \times 3 \times 1$  supercell.

We also performed different calculations using a  $2 \times 2 \times 5$  supercell with the in-plane lattice parameters fixed to the equilibrium value calculated without any defect and the out-of-plane parameter optimized to minimize the total energy: Such geometry has the same lateral dimension than the slab which has been used to study the interface with a Fe layer and its asymmetry allows to differentiate the effect of the localization of the oxygen vacancy in a SrO(001) or TiO<sub>2</sub>(001) atomic layer. In this condition, the formation energies become 5.18 eV and 5.68 eV, depending on if the oxygen vacancy is located in a TiO<sub>2</sub> or SrO (001) atomic layer.

The oxygen vacancy, in addition to its effect on the electronic structure, will distort the atomic structure. With the  $3 \times 3 \times 3$  supercell, we observe a structure with tilted oxygen octahedra. These tilts are preserved with the  $2 \times 2 \times 5$  supercell, only when the V<sub>O</sub> is located in the TiO<sub>2</sub> layer, while they disappear otherwise. It is important to note that the 221- $Pm\bar{3}m$  cubic perovskite describing SrTiO<sub>3</sub> changes its space group to respectively a 47- $Pmmm$  and 123- $P4/mmm$  space group, when the oxygen vacancy is in the TiO<sub>2</sub> or SrO (001) atomic layer. These different space groups result from the periodic and ordered structures we used for our calculations and by symmetry, the OOR are naturally, or not, allowed; a different result could be obtained for a bulk cell with a random distribution of the V<sub>O</sub> (hence preserving the cubic symmetry). The calculated OOR angles  $\alpha$  and  $\gamma$  are of approximately 7° around the  $a[100]$  axis (along the Ti-V<sub>O</sub>-Ti direction) and the  $c[001]$  axis, which is in agreement with previous reported calculations,<sup>35,64</sup> but is significantly larger than angles calculated with the HSE06 hybrid functional<sup>35</sup> or measured experimentally,<sup>65</sup> with values closer to 2°. The tilting angle  $\beta$  is almost 0° along

the  $b[010]$  direction (perpendicular to the Ti-V<sub>O</sub>-Ti direction). When the V<sub>O</sub> is located in a TiO<sub>2</sub> layer, the  $2 \times 2 \times 5$  tilted structure displays an averaged out-of-plane lattice parameter which is 0.2 % lower than the in-plane parameter, while the non-tilted structure obtained for a V<sub>O</sub> in a SrO plane is on the contrary in average 0.2 % higher. Phase transition accompanied by the appearance of ferroelectricity or octahedral tilts have already been reported or predicted in STO as a result of strain, doping dimensionality in thin-layer superlattices or near interfaces,<sup>23,64,66-69</sup> and have also been proposed in oxygen-deficient STO.<sup>24,35</sup>

A neutral oxygen vacancy is expected to release two electrons which will mainly localize themselves on the two Ti atoms first neighbors of the vacancy. A first calculation considering a simple  $3 \times 3 \times 3$  supercell shows the appearance of a gap state with a  $d_{z^2}$  symmetry and associated to a band energy lying 1.17 eV below the conduction band minimum (CBM). This first result is in agreement with results from the literature.<sup>25,34</sup> Considering the  $2 \times 2 \times 5$  cell, the  $d_{z^2}$  or  $d_{x^2-y^2}$  defect states are located approximately 1.65 eV under the CBM, and their energy dispersion in the first Brillouin zone will depend on their symmetry, and thus on the atomic plane in which the V<sub>O</sub> is located, as explained later. The difference of atomic distortion (with the appearance of OOR) does not affect the band gap width of STO.

*b. Variation of the  $U_{\text{eff}}$  parameter:* Keeping the  $2 \times 2 \times 5$  cell, we then made a systematic study of the  $U_{\text{eff}}$ -parameter dependence of our results by varying its value from 0 to 8 eV by steps of 2 eV and we reported in Fig 7a and b the calculated main characteristics of the atomic structures, which are the calculated in-plane lattice parameters and the OOR angles. As shown in Fig 7b, we can notice a significant increase of these angles, which almost double, from 4.1 to 7.3°, when  $U_{\text{eff}}$  varies from = 0 eV to 8 eV. This goes in hand with an increase of the in-plane-lattice parameter from  $a = 3.897$  Å to 3.950 Å.

The variation of  $U_{\text{eff}}$  has also an effect on the electronic structure. A summary of the evolution of the band energy at the  $\Gamma$  point near the Fermi level as a function of the value of  $U_{\text{eff}}$  is given in Fig. 7c and a detail of the calculated band structures for some specific values can be visualized in Fig. 8. Three different regimes can be distinguished:

1. For low  $U_{\text{eff}}$  values (0 – 2 eV), the electrons introduced by the neutral V<sub>O</sub> will populate the lower conduction bands, which have a  $d_{xy}$ ,  $d_{xz}$  or  $d_{yz}$  character (the minimum of the conduction band corresponding to a  $d_{xy}$  band at the  $\Gamma$  high-symmetry point) and they will be delocalized over the whole lattice. This regime is associated with a non-magnetic state and could be linked to the emergence of a two-dimensional electron gas near a surface or an interface.
2. For high  $U_{\text{eff}}$  values (6 – 8 eV), only one  $e_g$ -like band is fully occupied. When the V<sub>O</sub> is in a TiO<sub>2</sub>

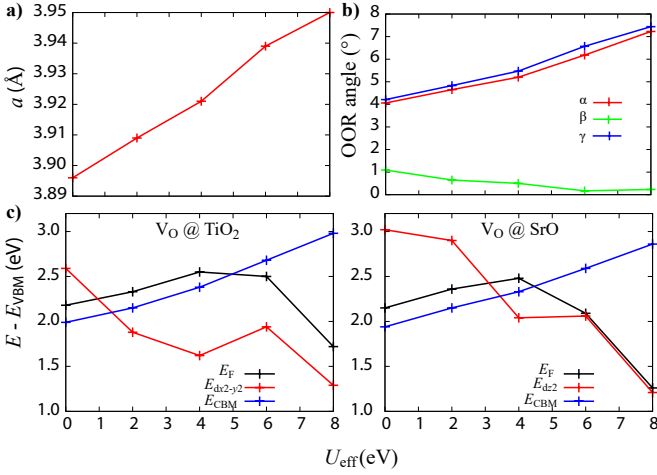


FIG. 7. Calculated SrTiO<sub>3</sub> atomic structure parameters and electronic band levels as a function of the  $U_{\text{eff}}$  parameter: a) Lattice parameter  $a$  calculated for the cubic bulk STO and used as the in-plane lattice parameter for the strained  $2 \times 2 \times 5$  bulk supercells and for the interface studies. b) OOR angles calculated when the  $V_{\text{O}}$  is located in a TiO<sub>2</sub> atomic layer in the  $2 \times 2 \times 5$  supercell. The angles  $\alpha$ ,  $\beta$  and  $\gamma$  are given respectively according to the 3 crystallographic axes  $a[100]$ ,  $b[010]$  and  $c[001]$ , which are parallel to the Ti-O chemical bounds. The values are averaged on every oxygen octahedra not included in the TiO<sub>2</sub> layer containing the  $V_{\text{O}}$ . c) Energy band levels at the  $\Gamma$  high-symmetry point. We define as  $E_{\text{VBM}}$  and  $E_{\text{CBM}}$  the energies of the states delimiting the band gap for the non-defective SrTiO<sub>3</sub> bulk compound, *i.e.* respectively the highest occupied O-p band and the lowest unoccupied Ti- $d_{xy}$  band. The given values are calculated when the  $V_{\text{O}}$  is located in a TiO<sub>2</sub> (left) or SrO (right) (001) atomic layer and the red curve corresponds to the energy of the  $d_{x^2-y^2}$  or  $d_{z^2}$  gap state.

atomic layer, these Ti atoms are located in the same layer, while they are in adjacent layers when the  $V_{\text{O}}$  is in a SrO atomic layer; this has for consequences that the occupied defect band will possess a different symmetry, *i.e.* respectively  $d_{x^2-y^2}$  or  $d_{z^2}$ , and have a wider energy dispersion ( $\sim 0.4$  eV) along the in-plane  $\Gamma$ -X-M directions for the former case. The charges are fully localized between the Ti atoms first-neighbors of the vacancy and the defective structure adopts an antiferromagnetic ordering.

- For intermediate  $U_{\text{eff}}$  values (around 4 eV), both ( $d_{xy}, d_{xz}, d_{yz}$ ) and  $d_{x^2-y^2}$  or  $d_{z^2}$  bands are partially occupied and a ferromagnetic ordering state appears as the most stable solution (when the oxygen vacancy is in a TiO<sub>2</sub> layer, the  $d_{x^2-y^2}$  band is already partially occupied for  $U_{\text{eff}} = 2$  eV).

At this point, we can conclude that the defective SrTiO<sub>3</sub> compound can be described both as a magnetic or non-magnetic system, associated with a conductive or insulating regime, depending on the energy-band local-

ization, which can be related to the electronic correlations described by the  $U_{\text{eff}}$  parameter and by the size of the supercell, that is the oxygen vacancy content. A last critical point which could also promote a regime or another would be the taking into account of a disordered distribution of the  $V_{\text{O}}$ , which we did not consider for the sake of simplicity.

In their study, Lin and Demkov<sup>70</sup> proposed with an Anderson impurity model that one electron of the  $V_{\text{O}}$  should occupy a localized hybrid  $d_{z^2}+p_z$  in-gap state and the other electron on the first conduction band; however, this magnetic impurity does not produce any net magnetic moment. Such model would give a result close to our calculation performed for  $U_{\text{eff}} = 4$  eV, except for the magnetic moment.

Altmeyer, *et al.*,<sup>71</sup> reported calculations on TiO<sub>2</sub> and SrO-terminated surfaces of SrTiO<sub>3</sub> with one or two oxygen vacancies and by using the commonly used values of  $U = 5$  eV and  $J = 0.64$  eV.<sup>72</sup> They found that the vacancies induce an in-gap state, 0.5 to 1.0 eV below the Fermi level, the energy depending on the positions of the vacancies according to the surface, on the surface termination and on the tendency to clusterize. This gap state corresponds to electron localized on the Ti atoms close from the  $V_{\text{O}}$  and are related to Ti spin magnetic moments. Ti atoms located further are on the contrary associated with delocalized and spin-polarized  $t_{2g}$  states, which can experience spin-orbit Rashba effects.

*c. Stability of charged defects:* For the sake of simplicity, we restrained our interface calculations to the study of neutral oxygen vacancies. This choice seems also reasonable as a first approximation, if we consider that the  $V_{\text{O}}$  is most likely to be located in a TiO<sub>2</sub> metallic interface layer. Further from the interface, where the STO remains insulating, the formation of charged oxygen vacancies would be possible. Locally, this would agree with the partial localization of the charges near the defect that we calculated.

The formation energy given in Eq. 2 can be re-written for one  $V_{\text{O}}$  in the bulk and with a charge state  $q$ :<sup>58,59</sup>

$$E_{\text{d}}(V_{\text{O}}^q) = E_{\text{bulk}}(V_{\text{O}}^q) - E_{\text{bulk}} - \frac{1}{2}(\mu_{\text{O}_2} + \Delta\mu_{\text{O}_2}) + qE_{\text{F}} \quad (\text{A1})$$

with the first terms having a similar meaning than in Eq. 2 and the last term corresponding to the chemical potential of the electric charge. The Fermi level  $E_{\text{F}}$  will be now considered as a parameter which can vary from 0 eV (when it is at the valence band maximum (VBM)) to 3.2 eV, the experimental value of the band gap of STO. The variations of the formation energies  $E_{\text{d}}(V_{\text{O}}^q)$  as a function of the position of the  $V_{\text{O}}$  and of  $E_{\text{F}}$  are given in Fig 9.

The calculated values shows that when the Fermi level is located close to the VBM, the oxygen vacancies will prefer to be in a charge state  $q = +2$  e. A transition to a neutral state  $q = 0$  e occurs at the energy  $\varepsilon(2+/0) \approx 2$  eV. Independently of the position of  $E_{\text{F}}$ , we can see

that the formation energy for a  $V_O$  is always lower when it is located in a  $TiO_2(001)$  atomic layer than in a SrO layer. It is interesting to note that the intermediate state of  $q = +1$  e is never stable according to this calculation, unless for  $E_F$  near the transition energy  $\varepsilon(2+/0)$ . For this state, we found that a ferromagnetic coupling with a spin magnetic moment of 0.2-0.4  $\mu_B$  for each of the two Ti atoms first neighbors of the  $V_O$ .

## Appendix B: SBH calculations

Different methods can be used to calculate the SBH (by aligning the core levels or calculating the averaged electrostatic potential for example); these methods give in general very close results,<sup>22</sup> which we verified for the perfect interfaces. In the present study, we preferred to use the LDOS to calculate the p-type SBH: to do so, we made the energy difference between the Fermi level which is set up by the Fe layer and the different gap states near the interface and the VBM at the center of the STO film. Considering that our STO layer has a sufficient thickness, the DOS at the center should be aligned to those of the bulk; otherwise some corrections would be necessary. As we can see from the Fig. 4b, the variation of the 1s core level energy of the oxygen atom at the center of the slab corresponds almost exactly to the calculated p-SBH, which indicates that such correction is negligible and our slab sufficiently thick. When including an oxygen vacancy, we verified that the band gap width at the center of the slab almost does not vary compared to the bulk value, allowing to use the LDOS to calculate the SBH.

If the bands from the Fe and STO layers are well aligned, the p-SBH can be correctly calculated. The n-SBH can then be obtained either by doing the difference between the Fermi level and the CBM at the center of the STO layer, if the STO gap is well calculated, or by doing the difference between the experimental band gap (3.2 eV) and the p-SBH. By considering the experimental band gap, the n-SBH is then approximately 0.4 eV higher than with the direct calculation with  $U_{\text{eff}} = 8$  eV.

Still if  $U_{\text{eff}} = 8$  eV, we found a preservation of the Schottky regime for most of the systems and we calculated the n- and p-SBH. It is difficult to choose a correct value for the  $U_{\text{eff}}$  parameter and compromises have to be made between a correct description of the vacancy electronic states and a sufficiently high value of the band gap near the Fermi level, this, by keeping in mind the limited size of our slab and the high vacancy content of our supercell. We chose to mostly focus on an artificially high value of  $U_{\text{eff}}$  as proposed in the Ref. 23 in order to give a general trend about the variation of the calculated SBH and to be consistent with the non-zero SBH measured by Catrou, *et al.* for the same interface.<sup>8</sup> As mentioned previously, with this approximation, we calculated an ionization potential of 5.40 eV and 3.78 eV, respectively for a  $TiO_2$ - and a SrO-terminated STO surfaces, which is close (even if lower) to the values of 6.71 eV and 4.41 eV, calculated

by Stevanović, *et al.*,<sup>73</sup> who have used a combination of GW and DFT+ $U$  methods. Experimental values have been reported to be in the range of 7.2-7.9 eV and may vary as a function of the oxygen adsorption/desorption: a larger ionization potential is measured for oxygen-rich conditions.<sup>74-76</sup>

As a lower value of  $U_{\text{eff}}$  is often used in the literature, we also provide the calculated SBH for  $U_{\text{eff}} = 0$  or 4 eV in Table II. For these lower  $U_{\text{eff}}$ , the SBH can only be calculated if the  $V_O$  is located in the  $TiO_2$  interface atomic layer; when it is located deeper in the film, the system is in an ohmic regime and the Fermi level crosses the conduction band of STO.

## Appendix C: Magnetic properties of the oxygen-deficient $TiO_2$ -terminated interfaces

The figure 10a shows both the variation of the spin magnetic moment  $m_s$  of the Ti and Fe atom at the  $TiO_2$ -terminated interface and of its absolute value when a  $V_O$  is introduced near the Fe/STO interface. The deviation is given according to the spin magnetic moment of the Ti or Fe atoms at the perfect interface (respectively  $-0.322 \mu_B$  and  $2.31 \mu_B$ ). Thanks to this figure, we will describe in details how the charge reconstruction resulting from the presence of the  $V_O$  affects the magnetic properties of the interface and we will derive a scenario which is summarized by the Fig. 10b. The description of the magnetic properties changes was beyond the scope of our paper, mostly focused on the formation of SBH, but it remains very close due to its link with the electronic structure. It may also be of interest to understand the effect that could have the  $V_O$ 's on the magnetoelectric properties of such interface.

Firstly, considering the absolute-value variation of the spin magnetic moments of the Ti atoms (solid blue curve) gives an approximated information about the charges transferred to the interface. When the  $V_O$  is in the  $TiO_2$  interface layer, we expect the MIGS's to be populated by the 2 electrons released by the neutral vacancy (*i.e.* 0.5 electron/Ti atom), which corresponds to the calculated increase of  $\delta\langle|m_s|\rangle_{\text{IF}}$  by  $0.475 \mu_B$ . When the  $V_O$  is located in atomic layers further from the interface, only a part of the released charges stays localized in the  $TiO_2$  layer first-neighbor of the vacancy, the other part being transferred to the  $TiO_2$  interface layer. The further the  $V_O$  from the interface is, the lower the amount of transferred charges; which is consistent with the decrease of the averaged absolute value of the spin magnetic moment of the interfacial Ti atoms from  $0.475 \mu_B$  (for the  $V_O$  at IF) to  $0.22 \mu_B$  (for the  $V_O$  at IF-3). Concerning the charges which are localized near the  $V_O$ , as their amount increases when the  $V_O$  is moved toward the center of the slab, we observe subsequently an increase of the induced spin magnetic moment on the first-neighbor Ti atoms, which reaches the value of  $-0.53 \mu_B$  for the two Ti atoms first-neighbor of the  $V_O$  and located in the  $TiO_2$ (IF-3)

layer. When the  $V_O$  is in a SrO layer, only the first-neighbor Ti atom in the adjacent  $TiO_2$  layer away from the interface possess a non-null induced magnetic moment of approximately  $-0.5 \mu_B$ , while the other Ti atom first-neighbor of the vacancy has a  $0 \mu_B$  spin magnetic moment. The aforementioned results stays qualitatively correct for a lower value of  $U_{\text{eff}}$  parameter (4 eV), even if quantitatively, the magnetic moment induced by the localized charge on the Ti atoms first-neighbor of the  $V_O$  is decreased by a factor 2 (when the  $V_O$  is at IF-3); in agreement with the bulk calculations described in the Appendix A, the lower the value of  $U_{\text{eff}}$  is, the more the charges will populate the CBM of STO, constituted of ( $d_{xy}, d_{xz}, d_{yz}$ ) bands instead of the localized  $d_{x^2-y^2}$  or  $d_{z^2}$  states. Still by comparing these results with the bulk calculations, the band bending induced by the interface adds a space separation of these two sets of occupied d bands and favors the occupation of the ( $d_{xy}, d_{xz}, d_{yz}$ ) bands near the interface.

If we analyze now the variation of the spin magnetic moment of the interfacial Ti atoms (dotted blue curve), which results from the charge transfer, we can have an additional information concerning some possible changes in the magnetic coupling between Ti atoms. It is for example possible to see that we have a change of its sign when the  $V_O$  is moved away from the IF (between IF and IF-0.5). When the  $V_O$  is located in the  $TiO_2$  interfacial layer, the spin magnetic moments on the Ti atoms are of  $+0.83 \mu_B$  and  $-0.76 \mu_B$ , corresponding to an almost com-

pensated in-plane antiferromagnetic ordering and leading to a nearly  $0 \mu_B$  value in average. When the  $V_O$  is moved in the IF-0.5 SrO layer, then only the Ti atom first-neighbor of the  $V_O$  will have the sign of its magnetic moment reversed (to a positive value), the other Ti atoms keeping a negative magnetic moment. In consequences,  $\delta\langle m_s \rangle_{\text{IF}}$  will decrease. Moving again the  $V_O$  further from the interface, the Ti atoms will feel less the effect of the  $V_O$  and they will remain all ferromagnetically coupled, with negative spin magnetic moments and a larger absolute value than the perfect interface ( $+0.22 \mu_B$  when the  $V_O$  is in the IF-3 layer). From the point where the  $V_O$  is located in the  $TiO_2$ (IF-1) layer,  $\delta\langle m_s \rangle_{\text{IF}}$  will then increase linearly due to the lowering of the transferred charge to the interface.

Finally, compared with the perfect  $TiO_2$ -terminated interface, the interfacial Fe spin magnetic moments (yellow curve) also undergo some slight variations as a function of the position of the oxygen vacancy. They increase from  $2.31$  to  $2.47 \mu_B$ , when an oxygen vacancy is located at the interface (IF layer). The variation of the Fe magnetic moment at the interface as a function of the  $V_O$  location is less than  $0.05 \mu_B$  for the calculated positions; it has a maximum of  $+0.22 \mu_B$  when the  $V_O$  is in the  $TiO_2$ (IF-1) layer, *i.e.* when the Ti-atom magnetic moments reach also a maximum (maximum of transferred charge with a ferromagnetic coupling), and it decreases toward  $0 \mu_B$  (*i.e.* the bulk value), when the  $V_O$  is moved toward the center of the slab.

- 
- \* remi.arras@cemes.fr
- <sup>1</sup> M. Jang, *Nano Converg.* **3**, 11 (2016).
  - <sup>2</sup> N. A. Al-Ahmadi, *Mater. Res. Express* **7**, 032001 (2020).
  - <sup>3</sup> M. W. Allen and S. M. Durbin, *Applied Physics Letters* **92**, 122110 (2008).
  - <sup>4</sup> T. Berthold, J. Rombach, T. Stauden, V. Polyakov, V. Cimalla, S. Krischok, O. Bierwagen, and M. Himmerlich, *J. App. Phys.* **120**, 245301 (2016).
  - <sup>5</sup> S. Müller, H. von Wenckstern, F. Schmidt, D. Splith, H. Frenzel, and M. Grundmann, *Semicond. Sci. Technol.* **32**, 065013 (2017).
  - <sup>6</sup> T. Schultz, S. Vogt, P. Schlupp, H. von Wenckstern, N. Koch, and M. Grundmann, *Phys. Rev. Applied* **9**, 064001 (2018).
  - <sup>7</sup> H. Stöcker, M. Zschornak, J. Seibt, F. Hanzig, S. Wintz, B. Abendroth, J. Kortus, and D. C. Meyer, *Appl. Phys. A* **100**, 437 (2010).
  - <sup>8</sup> P. Catrou, S. Tricot, G. Delhaye, J.-C. Le Breton, P. Turban, B. Lépine, and P. Schieffer, *Phys. Rev. B* **98**, 115402 (2018).
  - <sup>9</sup> F. Gunkel, D. V. Christensen, Y. Z. Chen, and N. Pryds, *Appl. Phys. Lett.* **116**, 120505 (2020).
  - <sup>10</sup> A. Ohtomo and H. Y. Hwang, *Nature* **427**, 423 (2004).
  - <sup>11</sup> A. F. Santander-Syro, O. Copie, T. Kondo, F. Fortuna, S. Pailhès, R. Weht, X. G. Qiu, F. Bertran, A. Nicolaou, A. Taleb-Ibrahimi, P. Le Fèvre, G. Herranz, M. Bibes, N. Reyren, Y. Apertet, P. Lecoeur, A. Barthélémy, and M. J. Rozenberg, *Nature* **469**, 189 (2011).
  - <sup>12</sup> T. C. Rödel, F. Fortuna, S. Sengupta, E. Frantzeskakis, P. L. Fèvre, F. Bertran, B. Mercey, S. Matzen, G. Agnus, T. Maroutian, P. Lecoeur, and A. F. Santander-Syro, *Advanced Materials* **28**, 1976 (2016).
  - <sup>13</sup> A. Kalabukhov, R. Gunnarsson, J. Börjesson, E. Olsson, T. Claeson, and D. Winkler, *Phys. Rev. B* **75**, 121404 (2007).
  - <sup>14</sup> W. Siemons, G. Koster, H. Yamamoto, W. A. Harrison, G. Lucovsky, T. H. Geballe, D. H. A. Blank, and M. R. Beasley, *Phys. Rev. Lett.* **98**, 196802 (2007).
  - <sup>15</sup> W. Meevasana, P. D. C. King, R. H. He, S.-K. Mo, M. Hashimoto, A. Tamai, P. Songsiriritthigul, F. Baumberger, and Z.-X. Shen, *Nature Mater.* **10**, 114 (2011).
  - <sup>16</sup> K. Szot, W. Speier, G. Bihlmayer, and R. Waser, *Nature Mater.* **5**, 312 (2006).
  - <sup>17</sup> M. Janousch, G. Meijer, U. Staub, B. Delley, S. Karg, and B. Andreasson, *Adv. Mater.* **19**, 2232 (2007).
  - <sup>18</sup> R. Muenstermann, T. Menke, R. Dittmann, S. Mi, C.-L. Jia, D. Park, and J. Mayer, *Jo. Appl. Phys.* **108**, 124504 (2010).
  - <sup>19</sup> R. T. Tung, *Appl. Phys. Rev.* **1**, 011304 (2014).
  - <sup>20</sup> N. F. Mott, *Proc. R. Soc. A* **171**, 27 (1939).
  - <sup>21</sup> W. Schottky, *Z. Phys.* **113**, 367 (1939).
  - <sup>22</sup> M. Mrovec, J.-M. Albina, B. Meyer, and C. Elsässer, *Phys. Rev. B* **79**, 245121 (2009).
  - <sup>23</sup> J. Lee, C. Lin, and A. A. Demkov, *Phys. Rev. B* **87**, 165103 (2013).
  - <sup>24</sup> X. Ma, Y. Dai, M. Li, and B. Huang, *Phys. Chem. Chem.*

- Phys. **19**, 774 (2017).
- <sup>25</sup> D. Ricci, G. Bano, G. Pacchioni, and F. Illas, Phys. Rev. B **68**, 224105 (2003).
- <sup>26</sup> J. P. Buban, H. Iddir, and S. Ögüt, Phys. Rev. B **69**, 180102 (2004).
- <sup>27</sup> M.-Q. Cai, Y.-J. Zhang, G.-W. Yang, Z. Yin, M.-S. Zhang, W.-Y. Hu, and Y.-G. Wang, J. Chem. Phys. **124**, 174701 (2006).
- <sup>28</sup> J. Carrasco, F. Illas, N. Lopez, E. A. Kotomin, Y. F. Zhukovskii, R. A. Evarestov, Y. A. Mastrikov, S. Piskunov, and J. Maier, Phys. Rev. B **73**, 064106 (2006).
- <sup>29</sup> D. D. Cuong, B. Lee, K. M. Choi, H.-S. Ahn, S. Han, and J. Lee, Phys. Rev. Lett. **98**, 115503 (2007).
- <sup>30</sup> V. E. Alexandrov, E. A. Kotomin, J. Maier, and R. A. Evarestov, Eur. Phys. J. B **72**, 53 (2009).
- <sup>31</sup> Y. Zhukovskii, E. Kotomin, S. Piskunov, and D. Ellis, Solid State Commun. **149**, 1359 (2009).
- <sup>32</sup> Z. Hou and K. Terakura, J. Phys. Soc. Jpn. **79**, 114704 (2010).
- <sup>33</sup> E. A. Kotomin, V. Alexandrov, D. Gryaznov, R. A. Evarestov, and J. Maier, Phys. Chem. Chem. Phys. **13**, 923 (2011).
- <sup>34</sup> C. Mitra, C. Lin, J. Robertson, and A. A. Demkov, Phys. Rev. B **86**, 155105 (2012).
- <sup>35</sup> M. Choi, F. Oba, Y. Kumagai, and I. Tanaka, Adv. Mater. **25**, 86 (2013).
- <sup>36</sup> A. R. Silva and G. M. Dalpian, J. Appl. Phys. **115**, 033710 (2014).
- <sup>37</sup> W. Sitaputra, N. Sivadas, M. Skowronski, D. Xiao, and R. M. Feenstra, Phys. Rev. B **91**, 205408 (2015).
- <sup>38</sup> J. J. Brown, Z. Ke, W. Geng, and A. J. Page, J. Phys. Chem. C **122**, 14590 (2018).
- <sup>39</sup> H. O. Jeschke, J. Shen, and R. Valentí, New Journal of Physics **17**, 023034 (2015).
- <sup>40</sup> G. Kresse and J. Hafner, Phys. Rev. B **49**, 14251 (1994).
- <sup>41</sup> G. Kresse and J. Furthmüller, Phys. Rev. B **54**, 11169 (1996).
- <sup>42</sup> P. E. Blöchl, Phys. Rev. B **50**, 17953 (1994).
- <sup>43</sup> G. I. Csonka, J. P. Perdew, A. Ruzsinszky, P. H. T. Philipsen, S. Lebègue, J. Paier, O. A. Vydrov, and J. G. Ángyán, Phys. Rev. B **79**, 155107 (2009).
- <sup>44</sup> S. L. Dudarev, G. A. Botton, S. Y. Savrasov, C. J. Humphreys, and A. P. Sutton, Phys. Rev. B **57**, 1505 (1998).
- <sup>45</sup> T. Ochs, S. Köstlmeier, and C. Elsässer, Integrated Ferroelectrics **32**, 267 (2001).
- <sup>46</sup> I. I. Oleinik, E. Y. Tsymbal, and D. G. Pettifor, Phys. Rev. B **65**, 020401 (2001).
- <sup>47</sup> A. Asthagiri and D. S. Sholl, J. Chem. Phys. **116**, 9914 (2002).
- <sup>48</sup> H. J. Monkhorst and J. D. Pack, Phys. Rev. B **13**, 5188 (1976).
- <sup>49</sup> M. Peressi, N. Binggeli, and A. Baldereschi, J. Phys. D: Appl. Phys. **31**, 1273 (1998).
- <sup>50</sup> M. Stengel, P. Aguado-Puente, N. A. Spaldin, and J. Junquera, Phys. Rev. B **83**, 235112 (2011).
- <sup>51</sup> D. Li, C. Barreteau, and A. Smogunov, Phys. Rev. B **93**, 144405 (2016).
- <sup>52</sup> C.-G. Duan, S. S. Jaswal, and E. Y. Tsymbal, Phys. Rev. Lett. **97**, 047201 (2006).
- <sup>53</sup> M. Fechner, I. V. Maznichenko, S. Ostanin, A. Ernst, J. Henk, P. Bruno, and I. Mertig, Phys. Rev. B **78**, 212406 (2008).
- <sup>54</sup> R. Arras and S. Cherifi-Hertel, ACS Applied Materials & Interfaces **11**, 34399 (2019), pMID: 31456387.
- <sup>55</sup> R. F. W. Bader, *Atoms in Molecules: a Quantum Theory* (New York: Oxford University Press, 1990).
- <sup>56</sup> E. Sanville, S. D. Kenny, R. Smith, and H. G., J. Comput. Chem. **28**, 899 (2007).
- <sup>57</sup> W. Tang, E. Sanville, and G. Henkelman, J. Phys.: Condens. Matter **21**, 084204 (2009).
- <sup>58</sup> C. G. Van de Walle and A. Janotti, Phys. Status Solidi B **248**, 19 (2011).
- <sup>59</sup> C. Freysoldt, B. Grabowski, T. Hickel, J. Neugebauer, G. Kresse, A. Janotti, and C. G. Van de Walle, Rev. Mod. Phys. **86**, 253 (2014).
- <sup>60</sup> T. Tamura, S. Ishibashi, K. Terakura, and H. Weng, Phys. Rev. B **80**, 195302 (2009).
- <sup>61</sup> L. Yu and A. Zunger, Nature Commun. **5**, 5118 (2014).
- <sup>62</sup> D. C. Vaz, E. Lesne, A. Sander, H. Naganuma, E. Jacquet, J. Santamaria, A. Barthélémy, and M. Bibes, Adv. Mater. **29**, 1700486 (2017).
- <sup>63</sup> "CRC Handbook of chemistry and physics, internet version," (CRC Press, Boca Raton, FL, 2005) pp. 12–124.
- <sup>64</sup> K. Uchida, S. Tsuneyuki, and T. Schimizu, Phys. Rev. B **68**, 174107 (2003).
- <sup>65</sup> T. Ikeda, T. Kobayashi, M. Takata, T. Takayama, and M. Sakata, Solid State Ionics **108**, 151 (1998).
- <sup>66</sup> W. Zhong and D. Vanderbilt, Phys. Rev. Lett. **74**, 2587 (1995).
- <sup>67</sup> E. Bousquet, M. Dawber, N. Stucki, C. Lichtensteiger, P. Hermet, S. Gariglio, J.-M. Triscone, and P. Ghosez, Nature **452**, 732 (2008).
- <sup>68</sup> C.-H. Lin, C.-M. Huang, and G. Y. Guo, J. Appl. Phys. **100**, 084104 (2006).
- <sup>69</sup> A. Vasudevarao, A. Kumar, L. Tian, J. H. Haeni, Y. L. Li, C.-J. Eklund, Q. X. Jia, R. Uecker, P. Reiche, K. M. Rabe, L. Q. Chen, D. G. Schlom, and V. Gopalan, Phys. Rev. Lett. **97**, 257602 (2006).
- <sup>70</sup> C. Lin and A. A. Demkov, Phys. Rev. Lett. **111**, 217601 (2013).
- <sup>71</sup> M. Altmeyer, H. O. Jeschke, O. Hijano-Cubelos, C. Martins, F. Lechermann, K. Koepf, A. F. Santander-Syro, M. J. Rozenberg, R. Valentí, and M. Gabay, Phys. Rev. Lett. **116**, 157203 (2016).
- <sup>72</sup> S. Okamoto, A. J. Millis, and N. A. Spaldin, Phys. Rev. Lett. **97**, 056802 (2006).
- <sup>73</sup> V. Stevanović, S. Lany, D. S. Ginley, W. Tumas, and A. Zunger, Phys. Chem. Chem. Phys. **16**, 3706 (2014).
- <sup>74</sup> V. E. Henrich, G. Dresselhaus, and H. J. Zeiger, Phys. Rev. B **17**, 4908 (1978).
- <sup>75</sup> J. Robertson and C. W. Chen, Appl. Phys. Lett. **74**, 1168 (1999).
- <sup>76</sup> R. Schafrank and A. Klein, Solid State Ion. **177**, 1659 (2006).

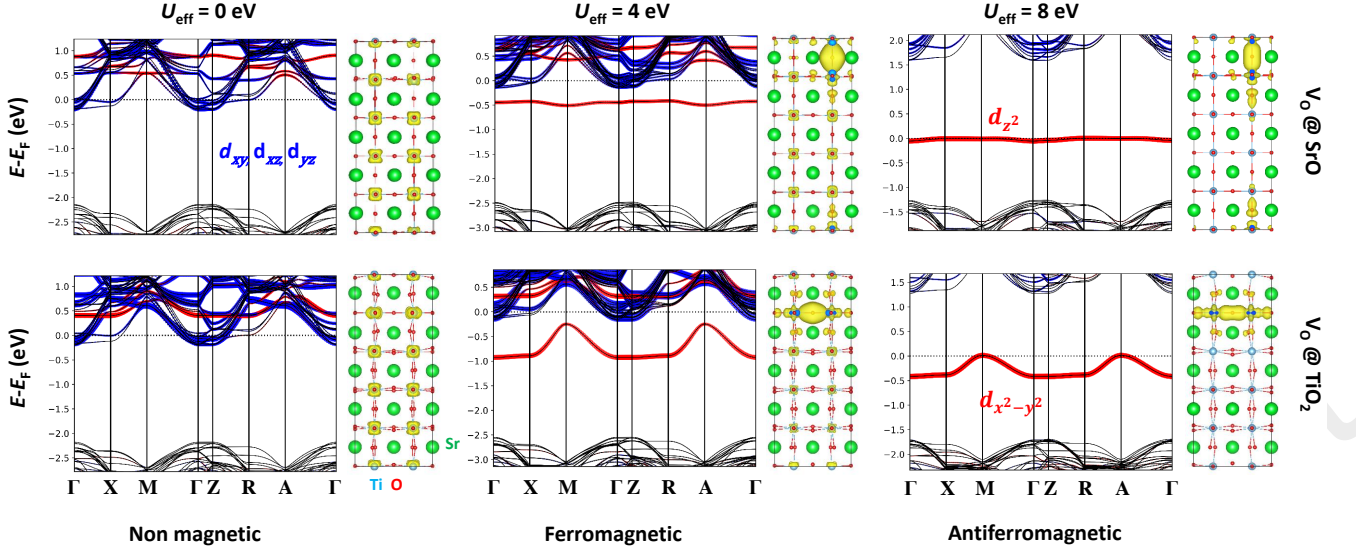


FIG. 8. Band structures and charge densities associated to the electronic states in the energy range between  $E_F - 1.5$  eV and  $E_F$ , calculated for different values of  $U_{\text{eff}}$  and the oxygen vacancy located in a  $\text{TiO}_2$  or  $\text{SrO}$  (001) atomic layer.

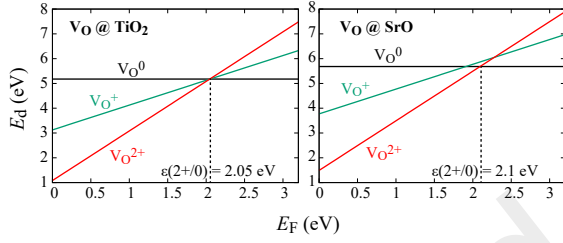


FIG. 9. Formation energies  $E_d(V_O^g)$  of an oxygen vacancy located either in a  $\text{TiO}_2$  (left) or a  $\text{SrO}$  (right) atomic layer as a function of the position of the Fermi level  $E_F$ . The energies were calculated using the  $2 \times 2 \times 5$  bulk supercell.

TiO <sub>2</sub> termination										
System	SBH → $U_{\text{eff}} \rightarrow$	p-			calculated n-			corrected n-		
		0	4	8	0	4	8	0	4	8
perfect IF		1.45	1.53	1.23	0.31	0.71	1.61	1.75	1.67	1.97
V <sub>O</sub> @ IF		1.87	1.87	1.64	0.0	0.42	1.23	1.33	1.33	1.56
V <sub>O</sub> @ IF-1.5		1.98	2.41	1.45	0.0	0.0	1.35	1.22	0.79	1.75
V <sub>O</sub> @ IF-2.5		2.05	2.50	2.37	0.0	0.0	0.48	1.15	0.70	0.83
V <sub>O</sub> @ IF-3		2.08	2.41	2.45	0.0	0.0	0.38	1.12	0.79	0.75
SrO termination										
System	SBH → $U_{\text{eff}} \rightarrow$	p-			calculated n-			corrected n-		
		0	4	8	0	4	8	0	4	8
perfect IF		1.97	2.36	2.80	0.00	0.00	0.01	1.23	0.84	0.40

TABLE II. p- and n-type SBH calculated for different values of  $U_{\text{eff}}$  (all energies are given in eV). The corrected n-type SBH is obtained by making the difference between the experimental band gap energy (of 3.2 eV) and the energy of the calculated p-type SBH.

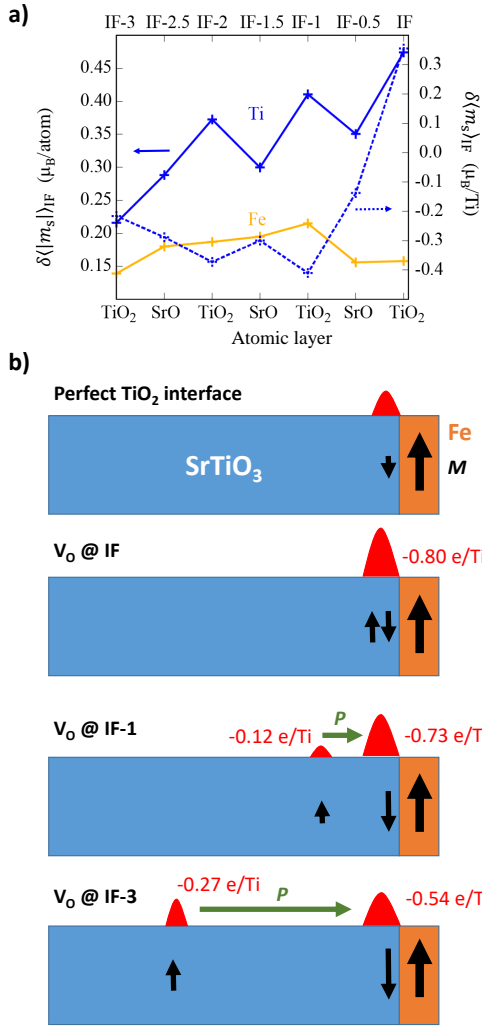


FIG. 10. a) Variation of the averaged spin magnetic moment  $\langle m_s \rangle$  (dotted line, right) and its absolute value (solid line, left)  $|m_s|$  of the interfacial Ti and Fe atoms as a function of the position of the oxygen vacancy near the TiO<sub>2</sub>-terminated interface. The values are given relatively to the moment of the same atoms at the perfect interface. b) Schematic representation of the charge localization (in red), leading to the emergence of an electric polarization  $P$  (green arrow) and of the magnetic ordering (black arrows) as a function of the  $V_O$  position.