



HAL
open science

Use of Solid-State NMR Spectroscopy for the Characterization of Molecular Structure and Dynamics in Solid Polymer and Hybrid Electrolytes

Gabrielle Foran, Nina Verdier, David Lepage, Cédric Malveau, Nicolas Dupré,
Mickaël Dollé

► **To cite this version:**

Gabrielle Foran, Nina Verdier, David Lepage, Cédric Malveau, Nicolas Dupré, et al.. Use of Solid-State NMR Spectroscopy for the Characterization of Molecular Structure and Dynamics in Solid Polymer and Hybrid Electrolytes. *Polymers*, 2021, 13 (8), pp.1207. 10.3390/polym13081207 . hal-03266215

HAL Id: hal-03266215

<https://hal.science/hal-03266215>

Submitted on 20 Oct 2021

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Use of Solid-State NMR Spectroscopy for the Characterization of Molecular Structure and Dynamics in Solid Polymer and Hybrid Electrolytes

Gabrielle Foran ^{1*}, Nina Verdier ¹, David Lepage ¹, Cédric Malveau ¹, Nicolas Dupré ² and Mickaël Dollé ^{1,*}

¹ Université de Montréal, Département of Chemistry, 1375 Avenue Thérèse-Lavoie-Roux, Montréal, Québec, Canada, H2V 0B3; mickael.dolle@umontreal.ca

² Université de Nantes, CNRS, Institut des Matériaux Jean Rouxel, IMN, F-44000 Nantes, France; Nicolas.Dupre@cnrs-imn.fr

* Correspondence: GF gabrielle.foran@umontreal.ca, MD mickael.dolle@umontreal.ca

Abstract: Solid-state NMR spectroscopy is an established experimental technique which is used for the characterization of structural and dynamic properties of materials in their native state. Many types of solid-state NMR experiments have been used to characterize both lithium-based and sodium-based solid polymer and polymer-ceramic hybrid electrolyte materials. This review describes several solid-state NMR experiments that are commonly employed in the analysis of these systems: pulse field gradient NMR, electrophoretic NMR, variable temperature T_1 relaxation, T_2 relaxation and linewidth analysis, exchange spectroscopy, cross polarization, Rotational Echo Double Resonance and isotope enrichment. In this review, each technique is introduced with a short description of the pulse sequence, and examples of experiments that have been performed in real solid-state polymer and/or hybrid electrolyte systems are provided. The results and conclusions of these experiments are discussed to inform readers of the strengths and weaknesses of each technique when applied to polymer and hybrid electrolyte systems. It is anticipated that this review may be used to aid in the selection of solid-state NMR experiments for the analysis of these systems.

Keywords: Solid-state NMR spectroscopy, polymer electrolytes, hybrid electrolytes, ion dynamics, electrochemistry

1. Introduction

Solid-state electrolytes for use in lithium batteries have been extensively studied as potential replacements to commercialized liquid electrolyte systems and have been touted as safer options as a result of being non-flammable, non-corrosive and non-volatile [1, 2]. There are three main classes of solid-state electrolytes: ceramic, polymer and ceramic-polymer hybrids [3]. Depending on their crystal structure and their composition, ceramic electrolytes tend to have good lithium ion conductivity (generally on the order of 10^{-4} S/cm at ambient temperature which is about one to two orders of magnitude lower than liquid electrolytes however, Kato et al. have prepared $\text{Li}_{9.54}\text{Si}_{11.74}\text{P}_{1.44}\text{S}_{11.7}\text{Cl}_{0.3}$ electrolytes with conductivities that rival those of liquid electrolytes) [4–8], good thermal stability and adequate mechanical strength to impede dendrite formation [9, 10]. However, these materials are rigid and tend to cause significant interfacial

44 resistance when in contact with solid electrodes [10]. Polymer electrolytes tend to have
45 good mechanical stability, minimal interfacial resistance with solid electrolytes and are
46 suitable for use in flexible battery applications [10]. However, lithium ion conductivity
47 tends to be much lower in most polymer systems at room temperature than in liquid or
48 some ceramic electrolytes (on the order of 10^{-8} to 10^{-6} S/cm at room temperature with
49 lithium transference numbers below 0.5) and dendrite formation may still occur [11].
50 Hybrid electrolytes, which contain both solid polymers and ceramic particles, were cre-
51 ated to capitalize on the advantages of both of these systems: they have higher lithium
52 conductivities (on the order of 10^{-5} to 10^{-4} S/cm at ambient temperature) [12–15] than
53 polymer electrolytes and are more flexible and interface compatible than ceramic elec-
54 trolytes [16]. The ceramic particles can be either active or inert, where active ceramics are
55 lithium conductors themselves and inert ceramics are non-conductive and are present to
56 decrease crystallinity in the polymer electrolyte. However, lithium conductivities tend to
57 remain lower than those of ceramic electrolytes as lithium ions must cross a complex se-
58 ries of polymer-ceramic interfaces for macroscopic-scale conductivity to occur [16]. In
59 addition to complexities due to the presence of different electrolyte materials and the
60 interfaces between them, microscale properties of the polymer electrolyte such as poros-
61 ity and pore radii, along with the salt concentration and the possibility of concentration
62 gradients can impact ionic conductivity in polymer and hybrid electrolytes [17, 18]. These
63 complexities can make hybrid systems difficult to characterize. In addition to lithi-
64 um-based all-solid-state batteries, similar systems have been developed using sodium as
65 the mobile species. Solid-state sodium batteries, which have been in development since
66 the 1980's, have been touted as being a more environmentally friendly technology rela-
67 tive to lithium-based batteries as a result of the higher abundance and lower cost of so-
68 dium versus lithium [19, 20]. Sodium polymer electrolytes tend to have ion conductivities
69 on the order of 10^{-7} to 10^{-6} S/cm at ambient temperature whereas sodium hybrid elec-
70 trolytes tend to have conductivities between 10^{-6} to 10^{-5} S/cm at the same temperature
71 [21–25]. Due to a growing interest in improving materials for flexible battery systems,
72 this review will focus on the characterization of molecular structure and ion mobility in
73 polymer and hybrid electrolyte systems. Many characterization techniques have been
74 employed in the analysis of these materials with some of the most frequently used being:
75 impedance spectroscopy, cyclic voltammetry, linear sweep voltammetry, differential
76 scanning calorimetry, thermal gravimetric analysis, Raman spectroscopy, infrared spec-
77 troscopy, microscopy techniques, x-ray diffraction and both solution-state and solid-state
78 nuclear magnetic resonance (NMR) spectroscopy [26–28]. This review will focus on the
79 use of solid-state NMR spectroscopy to analyze molecular structure and dynamics in
80 polymer and hybrid electrolytes. NMR spectroscopy can be performed on any nucleus
81 where spin, a quantized nuclear property, is non-zero [29]. Therefore, in addition to be-
82 ing non-destructive, NMR spectroscopy is an isotopically sensitive method for investi-
83 gating several nuclei that typically exist in solid electrolytes [28]. For example, nuclei
84 such as ${}^6\text{Li}$, ${}^7\text{Li}$, ${}^{19}\text{F}$ and ${}^{23}\text{Na}$ are generally used to study dynamic processes whereas ${}^1\text{H}$
85 and ${}^{13}\text{C}$ tend to be used to characterize polymer structure [30, 31]. NMR is particularly
86 suited to this task as it is sensitive to changes in local environments that occur on a mi-
87 crosecond to second timescale [30]. In addition to being sensitive to small changes in
88 chemical environments, solid-state NMR has the added advantage of allowing materials
89 in solid electrolyte systems to be analyzed in their native state.

90 The purpose of this document is to introduce a series of solid-state NMR spectros-
91 copy experiments that are commonly used in the analysis of solid polymer and hybrid
92 electrolytes to an audience who studies these systems but may not have an extensive
93 familiarity with solid-state NMR spectroscopy. To this end, each technique discussed in
94 this manuscript will be introduced starting with the pulse sequence, a description of
95 important setup parameters and specific advantages and disadvantages of applying the
96 technique to lithium- and sodium-based systems. Additionally, readers will be directed
97 to Table S1 (supplementary information) where information on required equipment and

98 experimental timescales are provided. Where applicable, comparisons between the NMR
99 technique and common electrochemical experiments will be provided. The purpose of
100 these comparisons is to inform the reader of differences in information that can be de-
101 termined via NMR and electrochemical methods as well as the advantages and disad-
102 vantages that are associated with each technique. Each section also includes examples of
103 previous uses of the NMR experiment in the analysis of real solid-state polymer or hy-
104 brid electrolyte systems with the goal of demonstrating the use of these techniques in real
105 systems. The significance of these works along with the findings and conclusions of their
106 authors are presented. Although similar reviews on crystalline electrolytes and reviews
107 focusing on specific polymers have been recently published, a comprehensive review on
108 the use of solid-state NMR spectroscopy for the analysis of polymer electrolytes has not
109 been produced in the past decade [32–34]. This work hopes to showcase the use of NMR
110 spectroscopy in the analysis of recent electrolyte systems and to provide a more thorough
111 description of the experiments themselves relative to what has been presented in previ-
112 ous work.

113 2. Solid State NMR Spectroscopy Techniques

114 2.1. Transference Number Determination

115 2.1.1. Pulse Field Gradient NMR

116 Pulse field gradient (PFG) NMR is an experiment that is used to measure the
117 self-diffusion coefficient of molecules or ions in solids or solutions where self-diffusion is
118 the random translational motion that is driven by internal kinetic energy [35]. These mo-
119 tions typically occur on a local scale and are therefore not necessarily equivalent to the
120 transference numbers, that can be directly measured via electrochemical methods, which
121 describe ion motion on a macroscopic scale [15, 36]. Additionally, the NMR technique
122 cannot distinguish single ions from poorly dissociated ion pairs and clusters which tends
123 to result in an underestimation of the self-diffusion coefficient [36–38].

124 PFG NMR experiments have previously been performed using a modified spin echo
125 pulse sequence (90° pulse - 180° pulse) where homogenous gradient pulses with duration
126 δ and strength g are applied on either side of the 180° pulse [39]. However, the experi-
127 ment is more commonly performed using a stimulated echo pulse sequence (Table S1).
128 This experiment is generally considered to be more efficient, as the magnetization lies
129 mainly along the z axis during the diffusion time (Δ), and is therefore subject to
130 spin-lattice relaxation time (T_1), instead of spin-spin relaxation time (T_2) as in the
131 spin-echo experiment. T_2 is usually significantly shorter than T_1 which is especially true
132 in inhomogeneous systems. A drawback of the stimulated pulse sequence is the loss of
133 half the signal, compared to the spin-echo experiment. The stimulated echo pulse se-
134 quence therefore allows the diffusion time to be longer [40]. The basic stimulated echo
135 PFG pulse sequence is comprised of three 90° pulses (Figure 1) [40, 41]. The application
136 of the first 90° pulse initiates the preparation phase of the experiment where the first gra-
137 dient pulse (with duration δ and magnitude g) is applied resulting in the Larmor fre-
138 quency becoming spatially labeled in the direction of the gradient [35, 39, 40]. The gra-
139 dient pulse is followed by the central pulse that causes the effective gradient to be zero as
140 only the z component of the magnetization vector is of interest [39, 40]. During this store
141 phase spins are allowed to diffuse for a time (Δ) which is usually dependent on the
142 spin-lattice relaxation of the system [39, 40]. Due to the effective gradient being zero, the
143 read and preparation phases are equivalent in terms of magnetization [40]. Therefore the
144 application of the second gradient pulse, which occurs during the read phase after the
145 application of a third 90° pulse, either cancels out the effects of the first gradient pulse if
146 no motion has occurred or results in an attenuation of the total signal that is proportional
147 to the translational motion that has taken place [35, 39, 40]. PFG NMR can be used to

measure diffusion along any axis depending on how the x, y and z gradients are used [35, 42].

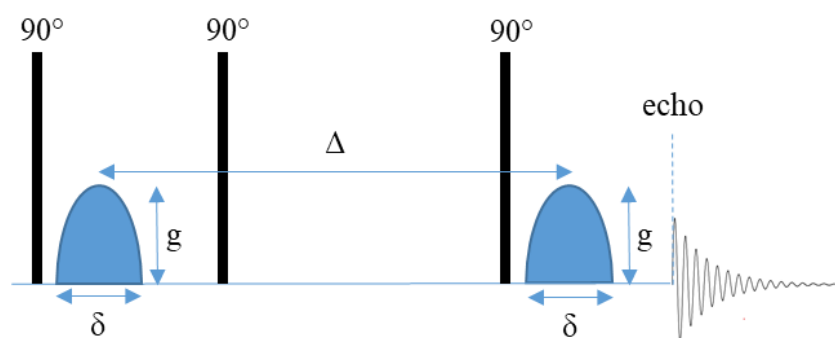


Figure 1. Stimulated echo PFG pulse sequence.

In the study of solid polymer or hybrid electrolytes, PFG NMR spectroscopy is commonly used to measure self-diffusion coefficients of anions and cations of the salt species as these are dissociated in the polymer or hybrid network. This is typically accomplished by performing ${}^7\text{Li}$ (cation mobility) and ${}^{19}\text{F}$ (anion mobility) experiments as both nuclei have high magnetic susceptibilities [43]. Additionally, PFG NMR can be performed on ${}^1\text{H}$ and ${}^{13}\text{C}$ to measure the mobility of the polymer chains as this motion can have a significant impact on the overall ion mobility in these systems [44–46]. PFG NMR is not usually used to measure sodium diffusion in sodium-conducting electrolytes because quadrupolar effects cause relaxation at ${}^{23}\text{Na}$ sites be much faster than relaxation at ${}^7\text{Li}$ sites [47]. Transport numbers for sodium ions therefore tend to be measured via electrochemical methods such as potentiostatic polarization [48]. Larger self-diffusion coefficients generally indicate higher ion mobility. Self-diffusion coefficients (D) can be calculated based on the degree of signal attenuation for each peak in the NMR spectrum using the Stejskal-Tanner equation (equation 1) [39, 42], where I and I_0 are the spectral integrals with and without the application of the gradient pulses, γ is the gyromagnetic ratio of the measured nucleus, g is the gradient strength, δ is the gradient pulse duration and Δ is the diffusion time. Usually, D is calculated by fitting the plot of signal intensity as a function of the gradient strength, keeping all delays and gradient duration constant. This allows the effects of relaxation on signal intensity to be removed. The Stejskal-Tanner equation is used for the spin echo experiment. When PFG NMR is performed using other pulse sequences, the Δ and δ quantities are modified to take the parameters of the experiment into account.

$$I = I_0 \exp\left(-\gamma^2 g^2 \delta^2 D \left(\Delta - \frac{\delta}{3}\right)\right) \quad (1)$$

Self-diffusion coefficients (D_+ the diffusion coefficient for the cation and D_- the diffusion coefficient for the anion), which are used to gauge the mobility of ions in a system, can also be used to calculate the activation energy for local-scale ion motion by plotting these values in a Arrhenius plot [49].

Additionally, the transference number (t_{NMR}^+), which is a measure of cation mobility relative to anion mobility (mole of cation transferred by migration per Faraday of charge) in a dilute system with no concentration gradients or ion association, can be calculated using self-diffusion coefficients (equation 2) where z_+ and z_- are the charges on the cation and anion respectively [50, 51]. This method for measuring the transference number works best in dilute systems as it assumes negligible ion-ion interactions and does not take into account the motion of associated species (sees everything as ions) [51].

$$t_{NMR}^+ = \frac{z_+ D_+}{z_+ D_+ - z_- D_-} \quad (2)$$

As mentioned previously, transference numbers can also be experimentally determined using electrochemical methods. A commonly used method is to couple a potentiostatic polarization with electrochemical impedance spectroscopy (EIS). This is typically done by employing the Bruce-Vincent method which involves polarizing a Li || Li cell using a small potential difference (~10 mV) until a constant current is reached [51, 52]. The resultant steady state conditions can then be used to calculate the transference number (t_{PP}) via equation 3 where ΔV is the applied potential difference, I_0 is the initial current, I_{ss} is the steady state current, R_0 is the resistance prior to polarization and R_{ss} is the resistance after polarization [51]. As for the NMR measurement, this approach is only valid in systems where the concentration gradient is negligible [51]. In more concentrated systems ($[Li^+]/[O] > 0.1$), the potentiostatic polarization experiment results in the diffusion of neutral ion pairs resulting in the over estimation of t_{PP} [51, 53].

$$t_{PP} = \frac{I_{ss}(\Delta V - I_0 R_0)}{I_0(\Delta V - I_{ss} R_{ss})} \quad (3)$$

To better represent ion diffusion in concentrated solutions, the Balsara-Newman method can be used [54]. The Balsara-Newman method for the determination of transference numbers is an extension of the Bruce-Vincent method that takes into account concentrated solution theory such that the contribution of ion pairs and clusters in bulk ionic motion can be accounted for [55]. With this approach, the transference number has a complex dependence on salt concentration and becomes negative when ion transport is dominated by ion clusters. While the Balsara-Newman method has the advantage of accurately measuring transference number in concentrated solutions, the method tends to be experimentally demanding as several parameters must be determined experimentally including the ionic conductivity (σ) from EIS, the steady-state transference number (t_{ss}) from potentiostatic polarization, the restricted diffusion coefficient (D) from PFG NMR and the potential of the concentrated cell (U). These parameters are combined with the bulk electrolyte concentration (c), the molality of the solution (m), ionic charge (z), the total number of ions when the salt dissociates (v), the number of cations when the salt dissociates (v_+) and Faraday's constant (F) to obtain the transference number (t_{Ne}) (equation 4).

$$t_{Ne} = 1 - \frac{(v_+ z_+)^2 2FDc}{v \sigma} \left(1 - \frac{1}{t_{ss}}\right) \left(\frac{d \ln m}{dU}\right) \quad (4)$$

The Hittorf method (also called Tubandt when applied to solids) is another electrochemical technique, suitable for use in concentrated solutions, that can be used in the experimental determination of transference numbers in solid polymer electrolytes [56]. The electrolyte is subdivided into sections where each fragment is placed between polarized electrodes and is subjected to polarization by a known charge [51, 57]. The transference number of the anion can be determined based on the change in the number of moles of the cation following polarization of the compartment that is closest to the cathode as shown in equation 5 where Δm is the change in the number of moles of cation, F is the Faraday constant and Q is the amount of charge that was passed through the compartment.

$$t_+ = 1 + \frac{\Delta m F}{Q} \quad (5)$$

Bruce et al. used the Hittorf method to measure t_+ in a poly(ethylene oxide) (PEO)-LiClO₄ electrolyte [57]. t_+ was found to be 0.06 which is lower than what has been previously reported by PFG NMR and potentiostatic polarization: 0.2 to 0.3 [57]. The differences between the transference numbers can be attributed to the fact that the Hittorf method does not measure the mobility of neutral species because the charge is not applied for a long enough period for a concentration gradient to develop in each subsection of the polymer. Therefore, transference numbers can be overestimated if significant quantities of ion pairs are formed [57]. Although the Hittorf method specifically measures charged species, it can be difficult to perform with polymer electrolyte samples

because PEO-based samples are often too adhesive to be easily subdivided into sections. Additionally, the technique requires a specialized electrochemical cell and the sample must be divided into at least four different compartments making it difficult to obtain accurate results [51].

Differences in transference numbers calculated via PFG NMR and various electrochemical techniques can be evaluated in the context of the dissociation ratio of the ionic species. The dissociation ratio describes the extent to which the ionic species are dissolved in a sample, with 1 indicating perfect dissociation and 0 indicating no dissociation [58]. As PFG NMR does not distinguish between dissociated and un-dissociated species, transference numbers reported via PFG NMR tend to be artificially higher than those determined via electrochemical methods as the motion of neutral pairs, dissociated ions and charged clusters is usually included in the measurement [58, 59]. It can therefore be concluded that in samples where similar transference numbers are achieved via NMR and electrochemical methods, nearly complete dissociation of the ionic species has been achieved.

Several examples of experiments that illustrate these differences between PFG NMR and electrochemical methods are described here. For example, a study of lithium bis(trifluoromethanesulfonyl)imide (LiTFSI)-doped PEO, which is discussed here for the purpose of demonstrating that different transference numbers can be determined for the same system using different experimental methods, showed that transference numbers as a function of the molar ratio of lithium ion to ether oxygens (r) varied between 0.17 and 0.30 based on PFG NMR data, between 0.06 and 0.26 based on potentiostatic polarization experiments and between -0.38 and 0.45 by the Balsara and Newman method, from $r = 0$ to $r = 0.3$ with the lowest value of -0.38 being observed at $r = 0.16$ (Figure 2) [53, 55]. The difference between the values calculated based on PFG NMR and potentiostatic polarization which depend on dilute solutions and those calculated based on the Balsara-Newman method suggest that the ionic species are not completely dissociated in this system.

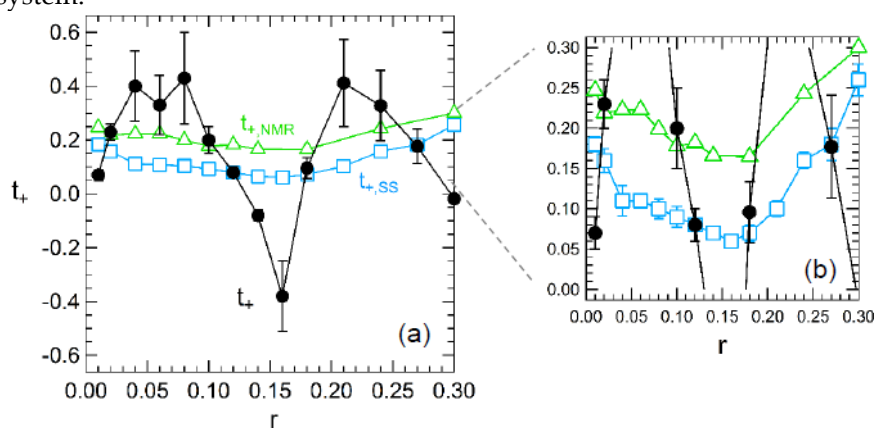


Figure 2. Transference number for Li^+ in a PEO-LiTFSI system as a function of the molar ratio of lithium ion to ether oxygens (r) measured via PFG NMR ($t_{+, \text{NMR}}$), potentiostatic polarization ($t_{+, \text{SS}}$) and the Balsara-Newman method (t_{+}). © Journal of the Electrochemical Society, 2017 [53].

However, transference numbers determined by electrochemical methods can also be subject to overestimation. This as was demonstrated by Sun et al., who showed that potentiostatic polarization can cause the diffusion of neutral species in concentrated systems and can result in an over estimation of the transference number via electrochemical methods [36]. Li^+ transference numbers in a poly(trimethylene carbonate)- ϵ -caprolactone copolymer were 0.32 via PFG NMR and 0.66 via potentiostatic polarization [36]. These differences were attributed to the migration of neutrally charged aggregates and could be avoided by using the Hittorf method [36]. Work by Tominaga and Yamazaki showed that the overestimation of transference numbers measured via

PFG NMR and potentiostatic polarization can even differ within the same study [60]. Their comparison of transference numbers in PEO-lithium bis(fluorosulfonyl)imide (LiFSI) (0.11 via potentiostatic polarization and 0.24 via NMR) and in poly(ethylene carbonate) (PEC)-LiFSI (0.54 via potentiostatic polarization and 0.24 via NMR) showed that the degree of ion dissociation in their prepared materials was not consistent [60]. These differences demonstrate that understanding the factors that influence transference numbers measured via both techniques is important when interpreting data.

Despite limitations related to the extent of salt dissociation, previous PFG NMR studies have demonstrated that Li^+ transference numbers can be dependent on both the segmental motion of polymer chains and the affinity of the lithium cation for the polymer. For example, Xu et al. and Sun et al. have found that cation mobility tends to be lower than anion mobility in LiTFSI-doped PEO at high lithium loading as the cation has increased affinity for the polymer matrix [27, 36]. As a result, segmental motion of polymer chains can impact short- and long-range Li^+ diffusion [36]. Therefore, PFG NMR experiments have been performed to demonstrate that interventions designed to increase segmental motion such as the synthesis of block co-polymers[61], the addition of inert ceramic fillers[60, 62] and increased sample temperature[63, 64] can increase the mobility of Li^+ in polymer electrolytes. The above experiments are important as they provide insight into the fact that polymer segment mobility, in addition to the extent of ion dissociation, contributes to observed transference numbers.

The above examples have focused on free ion diffusion: the random diffusion of ions that occurs as a result of thermal energy. However, PFG NMR can also be used to measure confined diffusion where the motion of ions is impeded by encountering boundaries [42]. The possibility to measure confined diffusion with three dimensional PFG NMR (using x, y and z gradients) may allow for more precise mapping of lithium ion diffusion in electrolyte systems [42]. Engelke et al. performed ^7Li PFG NMR to follow the three dimensional motion of a lithiated liquid electrolyte in a porous silicon wafer to map the pore structure of the wafer (Figure 3) [42]. The dimensions of the pores in the wafer were determined by calculating the mean square displacement of the lithium ions using their self-diffusion coefficients [42]. Although Engelke et al. performed their experiments on a confined liquid, similar methodology could be applied to polymer or hybrid electrolytes.


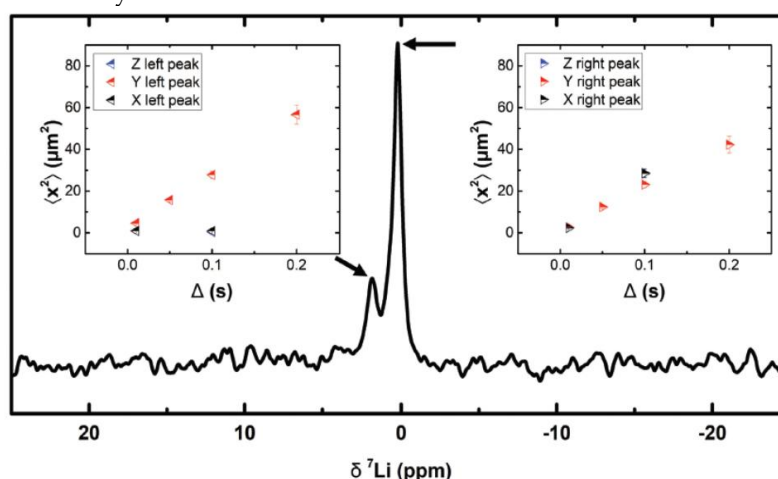


Figure 3: One dimensional slice from a ^7Li PFG NMR (7.1 T) experiment of lithiated liquid electrolyte in a porous silicon wafer. The inserts show calculated mean square displacements for each lithiated environment as a function of diffusion time. Reproduced from ref. [42] with permission from the PCCP Owner Societies.

310 The three-dimensional PFG NMR experiment could be particularly useful in the
 311 study of hybrid polymer electrolytes that contain inert ceramics as it could be used to
 312 determine the position of these particles and ascertain how Li^+ ions pass through the
 313 electrolyte. The analysis of electrolytes containing active ceramics is more complex as
 314 there is the potential for multiple mobile lithium species resulting in multiple diffusion
 315 coefficients. To demonstrate the use of PFG NMR in the analysis of a hybrid electrolyte, a
 316 system containing 70 % PEO, 12 % LiTFSI, 9 % $\text{Li}_{0.34}\text{La}_{0.51}\text{TiO}_3$ and 9 % succinonitrile (all
 317 weight percent) was analyzed. PFG NMR showed the existence of two mobile lithium
 318 species between 30 and 55 °C and a single mobile lithium species between 55 and 70 °C
 319 (Figure 4) [65]. Although a single peak was observed via 1D ^7Li NMR, the diffusion curve
 320 was best fit using two components between 30 and 55 °C [65].

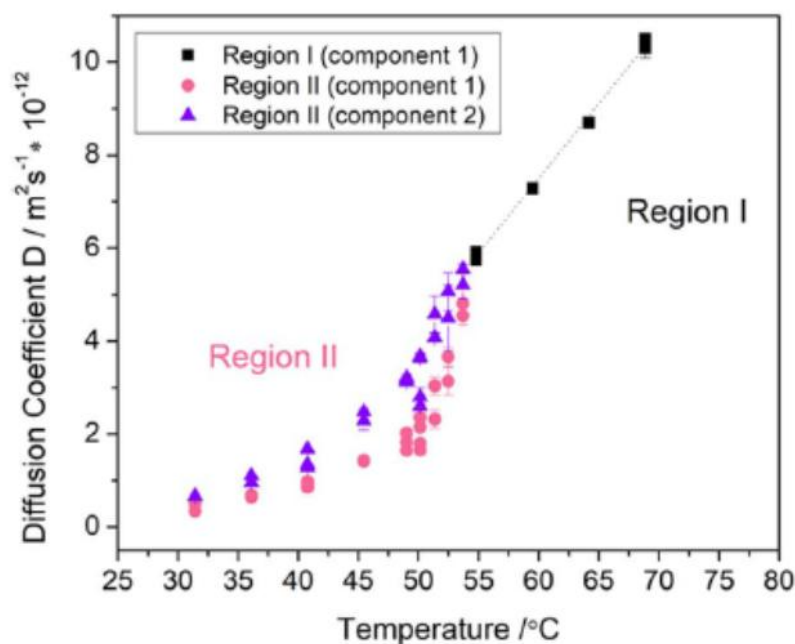

321
 322 **Figure 4:** Diffusion coefficients from the hybrid ceramic-polymer electrolyte as a function of tem-
 323 perature as determined by PFG NMR. © Journal of the Electrochemical Society, 2020 [65].

324 These diffusion coefficients were attributed to lithium conduction in the polymer
 325 and lithium conduction in the active ceramic. As the transition from two mobile lithium
 326 species to one mobile lithium species occurs around the melting point of PEO, it has been
 327 proposed that the associated decrease in polymer crystallinity results in lithium con-
 328 duction occurring preferentially through the polymer at high temperatures [65]. At lower
 329 temperatures, where the polymer is expected to be crystalline, the presence of two diffu-
 330 sion coefficients suggests that both the polymer and ceramic participate in lithium con-
 331 duction [65]. This example illustrates the primary advantage of PFG NMR over electro-
 332 chemical techniques: the ability to measure species-specific diffusion coefficients in mul-
 333 ti-component systems. This is particularly welcome in the analysis of hybrid electrolytes
 334 containing active ceramic fillers as both components of the electrolyte may participate in
 335 lithium transport. However, two-dimensional exchange spectroscopy experiments (de-
 336 scribed in section 2.3) would be needed to quantify ion exchange between these compo-
 337 nents.

338 2.1.2 Electrophoretic NMR

339
 340 Electrophoretic NMR is a one dimensional diffusion method, that is used to measure
 341 the flow of ions, from which transference numbers can be derived [66–68]. This experi-

mental method, involving a double stimulated echo and an applied electric field, has been previously used for the characterization of ion mobility in liquid electrolytes [66, 69]. However, it has had limited application in solid-state electrolytes outside of the work of Rosenwinkle and Schönhoff who used the method to determine transference numbers for lithium cation motion in PEO doped with various concentrations of LiTFSI [69]. The method is similar to PFG NMR in the sense that the pulse sequence is comprised of a series of gradient pulses with length δ and strength g within an echo comprised of 90° pulses (Table S1) (Figure 5). In the absence of the electric field, the random translational motion of mobile species in the direction of the magnetic field gradient results in random phase shifts and thus loss of net magnetic phase coherence, as in standard NMR diffusion experiments [66]. However, because the polarization of the electric field is switched after the first half of the pulse sequence to cancel out non-electrophoretic directional motion, only directional motion contributes to the measured phase shift (ϑ) [69].

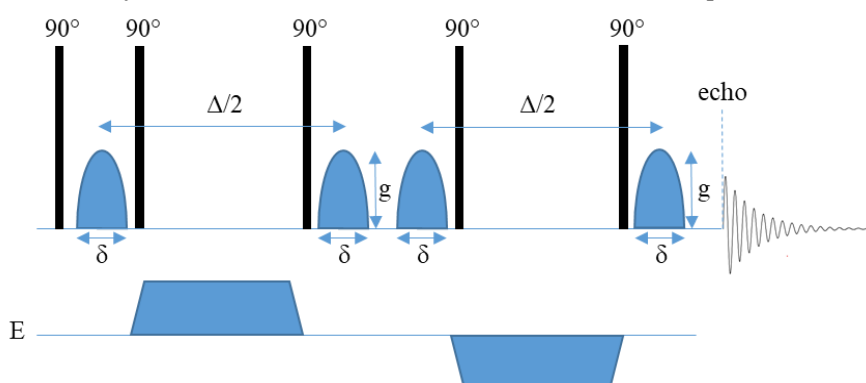


Figure 5: Electrophoretic NMR pulse sequence.

The electrophoretic drift of the observed species is signified by a phase shift (ϑ) in the NMR signal when the gradient strength (g) is changed. The phase shift can be calculated using equation 6 where γ is the gyromagnetic ratio of the observed nuclei, δ is the gradient pulse length, g is the gradient strength, Δ is the observation time, E is the strength of the applied electric field and μ is the electrophoretic mobility which is used to calculate the transference number.

$$\vartheta = \gamma \delta g \Delta E \mu \quad (6)$$

The electrophoretic mobility, which can be extracted from a plot of phase shift as a function of electric field strength using equation 6 is proportional to the drift velocity (v) and the electric field strength (equation 7). The drift velocity for free cations is defined as positive while the drift velocity for free anions is defined as negative. This relationship remains true when a plot of the phase shift as a function of gradient strength remains linear (Figure 6).

$$v = \mu E \quad (7)$$

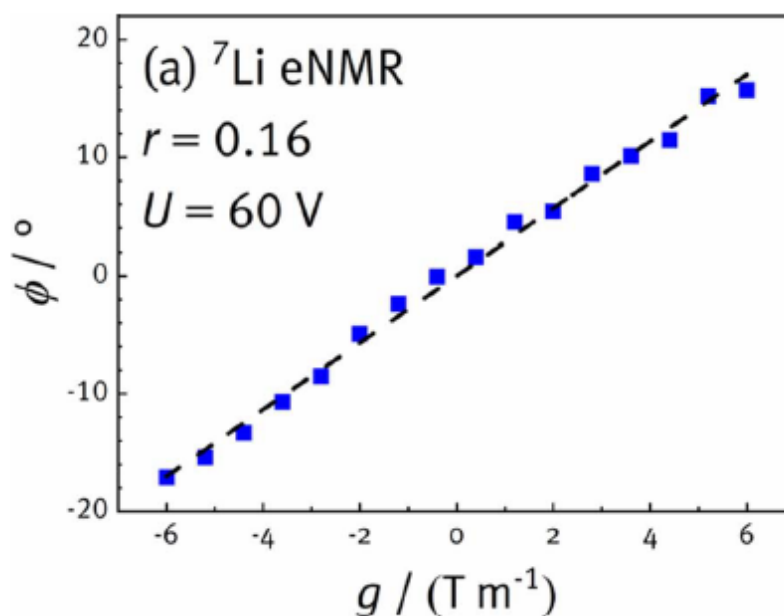


Figure 6: Plot of phase shift, determined via electrophoretic NMR, as a function of gradient strength for lithium cations in LiTFSI-doped PEO at 90 °C and a molar ratio of lithium to ether oxygen of 0.16. © Journal of the Electrochemical Society, 20 [69].

While the electrophoretic mobility can be impacted by electric field-induced changes in polymer chain orientation and electroosmotic drift, these effects can be canceled by extrapolating the phase shift as a function of field strength to zero electric field [69]. The electrophoretic mobilities of the cation and the anion (μ_+ and μ_-) can be used directly to calculate transference number (t_{eNMR}) using equation 8.

$$t_{eNMR} = \frac{\mu_+}{\mu_+ - \mu_-} \quad (8)$$

A PEO-LiTFSI system was used to demonstrate that transference numbers in solid systems can be determined via electrophoretic NMR. These experiments showed that cation mobility decreased with increasing salt content as a result of coordinating interactions between the salt and the polymer causing decreased side chain mobility [69]. The authors compared the t_{eNMR} values with transference numbers obtained via PFG NMR (t_{PFG}). Transference numbers obtained via both techniques were found to be in close agreement (t_{PFG} : 0.21, 0.17, 0.17 and t_{eNMR} : 0.23, 0.19, 0.15) for lithium at ether oxygen ratios of 0.06, 0.10 and 0.16 respectively, indicating that the samples contained mostly free cations [69]. As electrophoretic mobility is less impacted by the presence of ion pairs and agglomerations, it is anticipated that it can be used to provide more accurate values for transference numbers than PFG NMR in undiluted media. A direct comparison between electrophoretic NMR and electrochemical methods would be needed to determine the relative strengths of these methods for the determination of transference numbers in various types of samples. However, a lesser reliance on dilute systems suggests that electrophoretic NMR would be particularly useful in the analysis of systems with multiple mobile lithium environments such as hybrid electrolytes containing active ceramics.

2.2 Variable Temperature NMR

As lithium and sodium conductivities are temperature-dependent in many solid polymer and hybrid electrolytes, variable temperature NMR spectroscopy has been used to evaluate ion dynamics in these systems. Experiments that have been regularly performed for site-specific analysis of molecular dynamics include spin-lattice (T_1) relaxa-

tion, spin-spin (T_2) relaxation and linewidth analysis. Pulse sequences used to perform these techniques, along with examples of their use in the study of solid-state polymer and hybrid electrolytes, are discussed in this section. It must be noted that the larger quadrupolar moment of sodium, relative to lithium, means that quadrupolar coupling may have a significant impact on these parameters.

2.2.1 Spin Lattice Relaxation (T_1)

The application of radio frequency pulses during NMR experiments perturbs the magnetization vector away from its equilibrium position. The process through which the magnetization vector returns to equilibrium is termed relaxation [29]. In this work, the impact of temperature on T_1 relaxation for the study of ion mobility in solid electrolyte systems will be discussed. T_1 relaxation is characterized by the flow of energy out of the spin system and into the lattice and can be conceptualized as the time required for a perturbed magnetization vector to return to its equilibrium position following the application of a radio frequency pulse [29, 70]. T_1 relaxation generally occurs on the order of seconds to milliseconds but can be up to several minutes long for some nuclei in some environments. This relaxation process can be influenced by properties of the sample such as ion mobility and dipolar and quadrupolar interactions [70]. T_1 relaxation is typically measured using the inversion recovery pulse sequence (Table S1) (Figure 7) which is comprised of a 180° pulse which inverts all signals, a variable delay time (vd) during which relaxation back to equilibrium is allowed to occur and a 90° pulse for spectral acquisition [29].

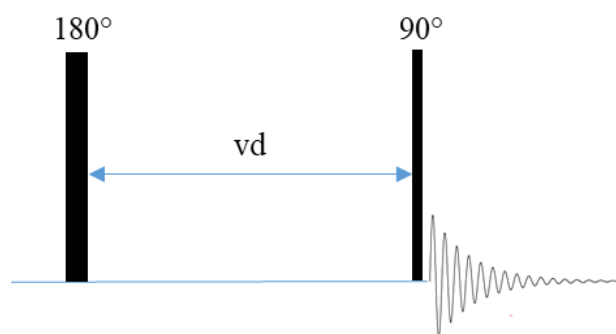


Figure 7: Inversion recovery pulse sequence.

This experiment produces a series of spectra of differing signal intensity as a function of variable delay time. T_1 relaxation can be calculated by fitting a plot of signal intensity as a function of variable delay time (vd) with one (or a series of) exponential functions. The fit can be performed using equation 9 where S_{vd} is the signal intensity at a given variable delay time and S_0 is the signal when vd is equal to zero [70, 71]. K is a fitted constant (with a value that is close to but does not exceed 2) that accounts for imperfect 180° pulses and the use of non-optimal repetition times.

$$S_{vd} = S_0 \left(1 - K e^{-\frac{vd}{T_1}} \right) \quad (9)$$

It is worth noting that as a quadrupolar nuclei (spin greater than $\frac{1}{2}$), T_1 build up curves for ^7Li spectra should in theory be fit using a double exponential function [72, 73]. However, as a result of the small quadrupolar moment of ^7Li (~ 0.04 MHz) [74], deviations from a single exponential fit are difficult to detect [72]. The T_1 relaxation time can also be quickly approximated using the variable delay time that results in net zero magnetization (T_{null}) (equation 10) [70].

$$T_1 = \frac{T_{null}}{\ln 2} \quad (10)$$

439
440
441
442
443
444
445
446
447
448
449
450
451
452
453
454
455
456
457
458
459
460
461
462
463
464
465
466
467
468
469
470

Meanwhile, ^{23}Na has a much larger quadrupolar moment which ranges between close to 0 and up to 7 MHz depending on the symmetry of the internal coordination sphere with highly symmetrical coordination spheres giving rise to low quadrupolar moments and coordination spheres with low symmetry giving rise to larger quadrupolar moments [75]. Therefore, T_1 build-up curves coming from sodium-based electrolytes may need to be fit using two or more exponentials depending on the magnitude of the quadrupolar moment.

NMR spectroscopy is highly sensitive to the impact of polymer chain dynamics on T_1 relaxation times [72]. As cation mobility and the mobility of the polymer backbone generally occur on the order of microseconds to seconds, these quantities can be evaluated via T_1 relaxation [76]. Many researchers have measured T_1 relaxation as a function of temperature to study the impact that this variable has on Li^+ and polymer chain segmental mobility [76, 77]. As activation energy for these processes can be calculated based on Arrhenius and/or Vogel-Tamman-Fulcher (VTF) plots of T_1 values, these quantities can be directly coupled with EIS data to provide a site-specific view of which motional processes contribute to long-range lithium conductivity [72, 78].

When calculating activation energies from T_1 values, temperature-dependent changes in ionic conductivity in polymer electrolytes must be taken into account as a result of changes that occur in polymer chain mobility above and below the glass transition temperature (T_g) [78]. At low temperatures, ionic conductivity in polymers is typically a result of the dissociated ionic pairs migrating through interstitial defects [78]. The activation energy for this process can be described by the Arrhenius behavior. Above T_g , ionic transport increases as a result of increased motion in the polymer side chains as they become less crystalline [79]. The activation energy for this process is best described by the VTF equation which was originally developed to describe the viscosity of supercooled liquid (Equation 11) [78], where σ is the ionic conductivity, A is a pre-exponential factor that is related to the concentration of the charge carrier, E_a is the activation energy which is typically related to the segmental motion of the polymer chains, R is the ideal gas constant, T_o is the Vogel temperature which is equal to the glass transition temperature in ideal glasses [80]. This is typically taken to be 50 °C below the glass transition temperature in polymer electrolytes [80].

$$\sigma = Ae^{\frac{E_a}{R(T-T_o)}} \quad (11)$$


471
472
473
474
475
476
477
478
479
480
481
482
483
484
485
486
487
488
489
490

Lower T_1 values are typically associated with increased mobility in solids. This is because spins that require changes in energy to relax can transfer that energy to or from motional processes [81]. An example that illustrates the impact motional processes on the rate of T_1 relaxation can be found in the work of Peng et al. who compared ^7Li T_1 relaxation times of a $\text{Li}_2\text{O}-\text{Al}_2\text{O}_3-\text{SiO}_2-\text{P}_2\text{O}_5-\text{TiO}_2-\text{GeO}_2$ (LICGC) ceramic, a mobile lithium-containing polymer phase and an immobile lithium-containing polymer phase in a PEO-LiTf-LICGC hybrid electrolyte [82]. T_1 relaxation times were longer for all lithium-containing phases of the hybrid electrolyte relative to the plain LICGC sample and a PEO-LiTf electrolyte [82]. The observed lower lithium ion mobility was attributed to a Lewis acid/based interaction between the polymer and the ceramic creating increased resistance in the ceramic-polymer interfacial layer [82]. Other interactions that can increase the rate of T_1 relaxation include paramagnetism and dipolar or quadrupolar coupling. Paramagnetic samples contain unpaired electrons which have large magnetic moments and are particularly effective at promoting relaxation [81]. Paramagnetism is particularly relevant in hybrid systems as many ceramics contain paramagnetic transition metals. Dipolar and/or quadrupolar coupling interactions tend to decrease T_1 relaxation times by providing an alternate pathway through which the relaxation process can occur [81]. This means that coupling interactions between ions and the membrane can also influence T_1 relaxation with stronger interactions resulting in decreasing T_1 . However, as lower T_1 values are typically associated with more mobile as opposed to mem-

brane-bound Li^+ ions, it can be assumed that motional processes have a more significant impact on T_1 relaxation in these systems than dipolar coupling interactions do.

Similar relationships between T_1 relaxation and site mobility have been observed in sodium-based polymer electrolytes. Schantz and Kakihana observed two sodium sites in a poly(propylene oxide) sample that contained NaCF_3SO_3 [83]. The observation of two distinct sites (one narrow and one broad) was attributed to the presence of two different nuclear coordination environments which were made visible by differences in quadrupolar coupling between these sites [75, 83]. The narrow site, which had a T_1 relaxation time of 9 μs , was attributed to mobile dissociated ions whereas the broad site (with a T_1 relaxation time of 13 ms) was attributed to ion pairs which tend to have low mobility [83]. Similar observations regarding the impact of motional processes on T_1 relaxation in sodium-based polymer systems were made by Pak et al. in a poly(propylene oxide)- $\text{NaB}(\text{C}_6\text{H}_5)_4$ system [84]. This sample also contained two sodium sites which could be attributed to mobile dissociated ions and less mobile ion pairs [84]. The T_1 relaxation time for the mobile site was about 10 ms at room temperature with the T_1 relaxation time for the broad site being about ten times longer. The difference between these relaxation times, and the faster T_1 relaxations times that are found in most sodium-containing polymer electrolytes such as those studied by Schantz and Kakihana, was stated to be a result of complexation between the sodium cation the large $\text{B}(\text{C}_6\text{H}_5)_4$ anion [83, 84]. It was additionally observed that the T_1 relaxation continued to decrease with increasing temperature and did not plateau at the T_g of poly(propylene oxide) as has been previously observed in several similar systems [84]. This suggests that ion motion primarily occurs independently of the motion of the polymer chain.

Sample mobilities can also be compared using a quantity called T_1 minimum. The T_1 minimum occurs at the temperature where the variations in relaxation rate are on the order of the Larmor frequency [30, 76]. The T_1 minimum can more directly be described as the temperature at which T_1 relaxation occurs most rapidly [81]. Species where the T_1 minimum occurs at a higher temperature have lower ion mobility as more energy must be transferred to or from the spin system for the maximum rate of T_1 relaxation to occur [30, 76, 81]. The correlation between differences in T_1 minimum and differences in ionic mobility was demonstrated through the analysis of LiClO_4 doped polyurethane-poly(dimethylsiloxane) copolymers [76]. In this system, the temperature where the T_1 minimum occurred was found to increase with increasing LiClO_4 loading (Figure 8a) [76]. These findings were well-correlated with impedance spectroscopy data as samples with T_1 minima at higher temperatures were found to be less conductive (Figure 8b) [76]. Although the determination of the T_1 minimum is generally time consuming and requires a probe and a variable temperature control with an extensive range, it can provide more information on the thermal properties of the polymer system in question than more typical T_1 measurements allowing for potential comparisons to differential scanning calorimetry data and the analysis of materials or samples that are not amenable to differential scanning calorimetry.

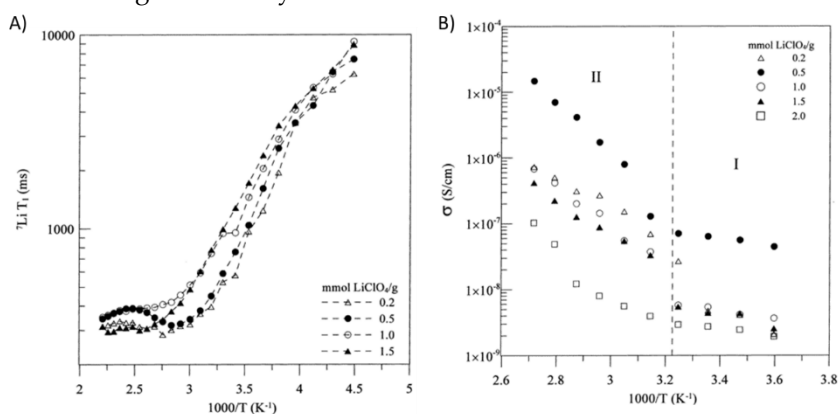

533 **Figure 8:** a) Variable temperature T_1 relaxation times for a series of LiClO_4 -doped polyurethane-poly(dimethylsiloxane) copolymers with various salt concentrations. b) Ionic conductivity as
534 a function of temperature for a series of LiClO_4 -doped polyurethane-poly(dimethylsiloxane) co-
535 polymers with various salt concentrations. Reprinted with permission from [76] Copyright 2002
536 American Chemical Society.
537

538
539 In the example presented in Figure 8, activation energies were calculated based on
540 the low temperature T_1 data by fitting the slope of an Arrhenius plot [76]. The activation
541 energy was found to increase from 6.3 to 11.3 kJ/mol when the molar ratio between the
542 lithium salt and the polyurethane-poly(dimethylsiloxane) copolymer was increased from
543 0.2 to 1.5 [76]. Activation energies were not calculated for the high temperature region as
544 a result of a kink in the T_1 data around 0 °C corresponding to the transition from Arrhe-
545 nius to VTF conductive behavior in the polymer sample thus indicating a link between
546 NMR and conductivity measurements [76].

547 Lin et al. and Daigle et al. have measured variable temperature T_1 in polyethylene
548 glycol (PEG)-based co-polymer systems containing lithium salts [31, 76]. In both cases T_1
549 was observed to decrease with increasing temperature indicating increased mobility of
550 both the polymer segment and the Li^+ ions. These results can often be correlated with
551 conductivity data. In these works, the low temperature portion of the T_1 buildup as a
552 function of temperature curve is used to calculate activation energies for Li^+ transport in
553 these systems, a method that can be used in samples that are not suitable for analysis via
554 EIS [85]. It is worth noting that this method does present some challenges as it requires
555 the ability to measure NMR spectra at low temperatures (down to -50 °C in Lin et al.[76])
556 since temperatures above about -10 °C are around the T_1 minimum where significant
557 changes in T_1 as a function of temperature no longer occur [85]. An additional challenge
558 is peak overlap. Despite differences in T_1 relaxation times between sites, Lin et al. re-
559 ported that it was difficult to deconvolute signals from the polymer backbone and the
560 mobile Li^+ species resulting in the reported activation energies potentially including
561 contributions from both species.

562 The differences between characterizing Li^+ mobility in a polymer electrolyte using
563 T_1 relaxation and EIS are illustrated in the outcome of the study by Jeon and Kwak [72].
564 The variable temperature T_1 analysis of a poly(vinylidene fluo-
565 ride-co-hexafluoropropylene) network doped with P(EO-EC)- LiCF_3SO_3 between -40 and
566 70 °C showed that T_1 relaxation time and T_1 derived activation energy for lithium motion
567 decreased with increasing temperature and increasing P(EO-EC)- LiCF_3SO_3 doping [72].
568 Both are consistent with increased lithium mobility. Decreasing activation energy was
569 also observed with increasing temperature and increasing P(EO-EC)- LiCF_3SO_3 doping
570 via EIS [72]. However, the activation energies were not equal. The activation energy that
571 was calculated based on T_1 relaxation (9.8-13.1 kJmol⁻¹) was lower than that which was
572 calculated based on lithium conductivity (41.2-50.1 kJmol⁻¹) [72].


573 The difference in activation energies is a result of NMR and EIS measuring ion mo-
574 tion on different length scales. NMR effectively measures local-scale mobility while EIS
575 measures global mobility. It is anticipated that the higher activation energy as measured
576 by EIS is a result of more energy being required for long-range motion than for local-scale
577 motion [72]. Additionally, in samples with multiple lithiated chemical environments,
578 site-specific activation energies, which may not contribute to global ionic conductivity,
579 can be determined by NMR. This is not the case with impedance spectroscopy of polymer
580 samples as one conductivity value typically represents all components of a sample that
581 are in the same phase and that contribute to long-range ionic conductivity. There may
582 however be the possibility of distinguishing multiple phases via EIS in ceramic or hybrid
583 samples due to the presence of multiple semi-circles. The difference in motional scale,
584 along with the possibility to measure site-specific mobility in NMR are the reasons why
585 activation energies calculated via these techniques may not match and should not be

586 compared directly. However, comparing these properties qualitatively (increasing or
 587 decreasing) can be done to support claims of increased or decreased mobility in a sample.
 588

589 2.2.2 Spin-Spin Relaxation (T_2)

590
 591 T_2 relaxation, also called transverse relaxation or spin-spin relaxation, is the relaxa-
 592 tion of the x and y components of the magnetization vector without energy transfer to the
 593 lattice [70]. This process occurs as the magnetization vector precesses about the xy plane
 594 after a pulse has been applied [70]. During this time, individual spins that make up the
 595 magnetization vector fan out across the xy plane which destroys coherence (the orienta-
 596 tion of magnetization in the same direction) and can result in line broadening. This pro-
 597 cess is due to small fluctuations of local microscopic magnetic field caused by local mo-
 598 bility. This effect, which depends on the orientation of the nucleus with respect to the
 599 magnetic field and the scalar coupling in electrons is particularly apparent when T_2 re-
 600 laxation times are short [70]. Short T_2 relaxation times can cause significant signal loss if
 601 the T_2 is shorter than the delay times that are used in some pulse sequences. T_2 relaxation
 602 times can be particularly affected by the quadrupolar interaction as it is also orientation
 603 dependent and heavily dependent on the structure of the local coordination sphere [86].
 604 Changes in the quadrupolar interaction tend to minimize T_2 relaxation time which causes
 605 significant line broadening [86]. Line broadening can complicate spectral interpretation
 606 by causing peaks originating from distinct chemical environments to overlap.

607 T_2 relaxation can be measured using the spin-echo pulse sequence which is com-
 608 prised of a 90° pulse followed by a delay time (τ), a 180° pulse and a second delay period
 609 (τ) [87, 88]. However, the Carr-Purcell-Meiboom-Gill (CPMG) pulse sequence (Table S1)
 610 is probably more commonly used to measure T_2 relaxation [89, 90]. This pulse sequence
 611 begins with a 90° pulse, a delay period (τ) and a 180° pulse as in the spin echo sequence,
 612 but also includes a train of 180° pulses at $2n\tau$ delay periods following the first 180° pulse
 613 which results in a series of spin echoes that occur at time $2n\tau$ (Figure 9) [90]. The echo
 614 train continues until the signal has decayed [89, 90]. The advantage of using the CPMG
 615 pulse sequence over the spin echo pulse sequence is that the train of 180° pulses mini-
 616 mizes the potential loss of magnetization due to random spin diffusion, which prevents
 617 complete magnetization refocusing [90]. Both the spin-echo and the CPMG pulse se-
 618 quences are used in some of the experiments that are discussed here.

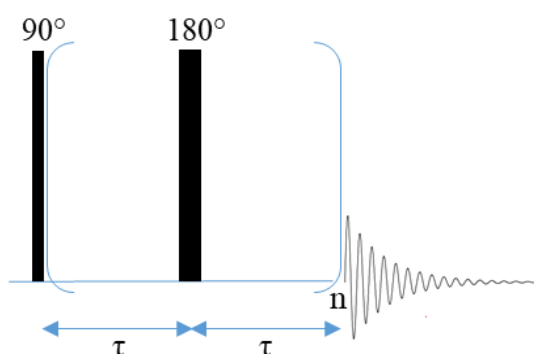

619
 620 **Figure 9:** CPMG pulse sequence.

621 In single-pulse experiment, observed signal decay is caused by a combination of T_2
 622 relaxation and decay due to magnetic field inhomogeneity[29]. However, the spin echo
 623 pulse sequence allows losses due to field inhomogeneity to be recovered. Following the
 624 application of the 90° pulse, magnetic field inhomogeneity causes spins in regions of rel-
 625 atively high magnetic field to precess faster than spins that are in a region of relatively

low magnetic field [29]. After the spins have evolved for time τ , the phases of magnetization of different regions are sufficiently different to cause a decrease in the overall magnetization. This is illustrated in equation 12 where T_2^* is the observed decay, T_2 is the transverse magnetization, γ is the gyromagnetic ratio and ΔH_0 is the inhomogeneity of the magnetic field.

$$\frac{1}{T_2^*} = \frac{1}{T_2} + \gamma \Delta H_0 \quad (12)$$

However, the spins in each individual region of the magnetic field are still coherent and precessing in the transverse plane [29]. This dephasing effect is then reversed by the application of a 180° pulse as all transverse spins are reflected in the direction of the applied pulse [29]. This reverses the motion of the spins and, because faster spins get de-phased at a faster rate, after the second delay period all spins are back in phase and the total magnetization reaches a maximum (yielding a spin echo) [89]. The height of the spin echo shows what the free induction decay would have been at a time of 2τ if no field inhomogeneities were present [90]. For the CPMG pulse sequence, 180° pulses are repeated until the echo has completely decayed. In this case, T_2 is calculated using equation 13 where $I(2n\tau)$ is the signal after the n^{th} echo and $I(0)$ is the initial signal.

$$I(2n\tau) = I(0)e^{\left(\frac{-2n\tau}{T_2}\right)} \quad (13)$$

T_2 relaxation, as determined using the spin-echo pulse sequence, has been used in a few instances in the analysis of polymer films as an alternative method for measuring the effects of electrolyte hydration and lithium salt addition [88, 91]. This was the case in the work of Donoso et al. who compared T_2 values in hydrated and anhydrous PEO-LiBF₄ polymer electrolytes [91]. T_2 relaxation was found to increase with hydration with the anhydrous film having a T_2 of 45 μs and the hydrated film having a T_2 of 130 μs [91]. The increase in T_2 relaxation time was attributed to the fact that water is predicted to act as a plasticizer in this system by both increasing the mobility of the polymer chains and by increasing the volume of the mobile segments [91]. The fact that changes in polymer chain mobility can be observed via T_2 relaxation was also used by Forsyth et al. as an alternative means of determining T_g in PAN-LiTf films that were not amenable for analysis via DSC [88]. The T_g was identified as the temperature at which a large increase in T_2 , which was correlated with increased polymer chain mobility, was observed (Figure 10). In this case the pure polymer had a T_g of 107 $^\circ\text{C}$ whereas the sample containing 67 % LiTf had a T_g of 72 $^\circ\text{C}$ showing that increased salt content increased polymer plasticity [88]. It is noted by the authors that the T_g value for the pure PAN sample is about 10 degrees higher than the standard DSC value. The above studies show that T_2 relaxation can be used instead of or in combination with differential scanning calorimetry to elucidate the impact of temperature on polymer mobility and thermal properties.

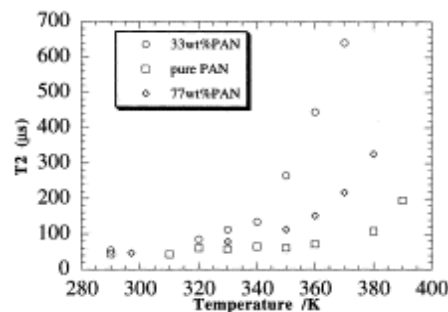


Figure 10: T_2 relaxation as a function of temperature for pure PAN and PAN electrolytes containing 30 and 67 % by weight LiTf. T_g was designated as the temperature where T_2 relaxation changed significantly which was indicative of significant polymer chain motion. Reprinted from [88] Copyright 2000 with permission from Elsevier.

666
667
668
669
670
671
672
673
674
675
676
677
678
679
680
681
682
683
684
685
686
687
688
689
690
691
692
693
694
695
696
697

The Carr-Purcell pulse sequence has been used to identify environments with different mobilities in polymer electrolytes. The ability to identify and characterize multiple species in the same sample is typically one of the advantages of using NMR spectroscopy over electrochemical techniques. This has been demonstrated in the context of T_2 relaxation by several authors including Franco et al. who found that segments in a PEO polymer containing LiClO_4 and 20 wt% carbon black have two distinct mobilities via ^1H NMR [92]. The site with the longer T_2 was attributed to the mobile polymer chains and the site with the shorter T_2 was attributed to the immobile backbone [92]. A similar experiment was performed by Kwaks et al. who measured ^1H T_2 in polymer electrolytes comprised of poly(oligo oxyethylene methacrylate) and LiTFSI [93]. They found three separate T_2 values which corresponded to the mobile side chain ($T_2 = 70$ ms), the interface between the polymer chains ($T_2 = 10$ ms) and the immobile polymer backbone ($T_2 = 1$ ms) [93]. The characterization of three distinct lithium environments in a single system would not have been possible via most electrochemical methods. T_2 relaxation was also used by Kidd et al. to identify two distinct lithium environments in PEO-based polymer electrolytes that are crosslinked to polyvinylidene fluoride (PVDF) filaments [94]. These materials were soaked in a mixture of ethylene carbonate, dimethyl carbonate and lithium triflate and contained 10, 20 or 30 wt% pentaerythritol triacrylate (PETA). Two distinct lithium environments, one with a long T_2 (195-310 ms depending on PETA content) and another with a shorter T_2 (12-21 ms depending on PETA content) were identified by the authors [94]. The length of the lithium environment with short T_2 was estimated at $3\ \mu\text{m}$ based on a combination of the 2τ delay period and diffusion data from PFG experiments [94]. This finding, and the fact that the fraction of the long T_2 environment increased from 26 to 79 % when the PETA weight percent was increased from 10 to 30, allowed the environment with the short T_2 being assigned to the PVDF filaments and the environment with long T_2 being assigned to the PEO between the filaments. The results of the above studies suggest that T_2 relaxation measurements can be performed as a method of determining, among other things, the number of sites present in a sample, their mobilities and their thermal properties.

2.2.3 Linewidth

698
699
700
701
702
703
704
705
706
707
708
709
710
711
712
713
714
715
716

Similar to T_1 or T_2 relaxation, changes in spectral linewidth as a function of temperature can be compared to assess the relative mobility of species in a sample with narrower lineshapes indicating increased mobility [95, 96]. The analysis involves fitting individual peaks in an NMR spectrum and measuring the full width at half maximum (FWHM) of each site. This technique is widely used to assess mobility as it does not necessarily require complex NMR experiments to be performed (Table S1). However, techniques such as magic angle spinning (MAS) and proton decoupling are often used to produce narrower lineshapes which can be more readily deconvoluted and fit. While changes in FWHM can be used to quantify the relative mobilities of sites in a sample under the same experimental conditions, this technique is not suitable for the direct quantitative comparison of ion dynamics when different NMR experiments are performed as experimental parameters can impact FWHM. However, linewidth analysis can be used to quantitatively assess site-specific ionic motion between samples and/or under different experimental conditions if changes in FWHM are used to calculate activation energy. Activation energies can be calculated from Arrhenius plots of FWHM as a function of temperature (Figure 11) and, like T_1 relaxation, linewidth analysis can be coupled with electrochemical impedance spectroscopy measurements to describe the contributions of site-specific motions to global lithium transport [76, 97, 98].


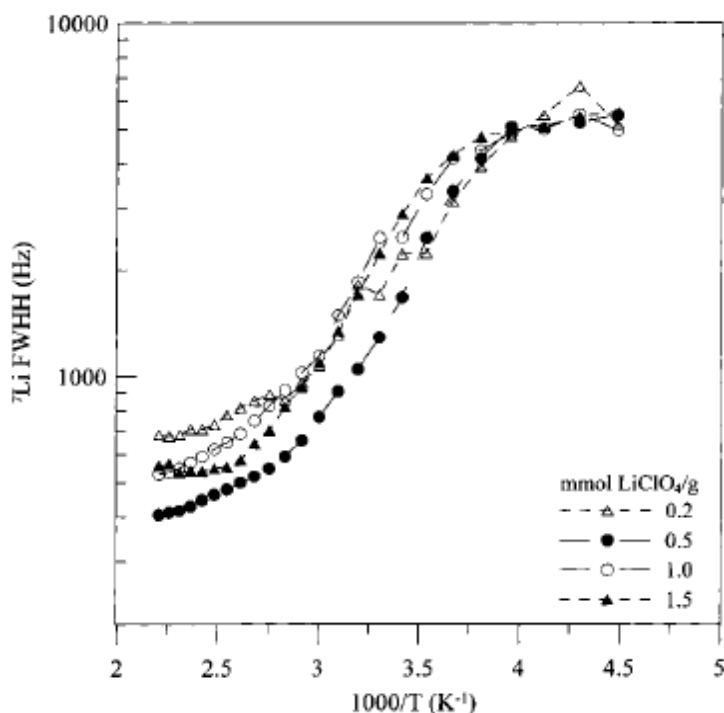


Figure 11: Arrhenius plot based on FWHM measurement from a series of PEO-polydimethylsiloxane (PDMS) films doped with varying amounts of LiClO_4 . Reprinted with permission from [76] Copyright 2002 American Chemical Society.

Linewidth analysis is commonly used to assess the mobility of sodium sites in solid polymer electrolytes. However, as the ^{23}Na quadrupolar moment can be significant (up to about 7 MHz), these interactions can significantly impact linewidth making it difficult to discern which contributions to the total linewidth come from temperature-dependent ion mobility and which are caused by second order quadrupolar effects [99]. In addition to impacting linewidth, quadrupolar interactions can also alter the chemical shift from its isotropic value [100]. Despite the potential drawbacks of the quadrupolar interaction in sodium-based systems, the quadrupolar contribution to the linewidth can reveal a significant quantity of information about the sodium sites' immediate coordination environment.

Variable temperature lineshape analysis has been used to evaluate species mobility in complex polymer electrolyte systems [101]. An example of this is the use of ^7Li NMR to evaluate differences in ion mobility in a polymer-gel electrolyte mixture that was comprised of polyacrylonitrile (PAN), polypropylene carbonate, ethylene carbonate and LiClO_4 salt [95]. In this case, significant line narrowing was observed in the gel component while the peak corresponding to the PAN remained broad, signaling low ion mobility in the polymer component [95]. In addition to probing component mobility in polymer-gel systems, variable temperature linewidth analysis has also been used to evaluate PEO systems containing inert and active ceramic dopants [13, 96, 102]. Chung et al. prepared PEO- LiClO_4 films containing 10 wt% TiO_2 [96]. The addition of the ceramic nanoparticles resulted in an increase in the FWHM relative to the TiO_2 -free sample. This was attributed to decreased segmental motion of the polymer chains as a result of cross-linking between the polymer and the TiO_2 nanoparticles [96]. Bonizzoni et al. used variable temperature ^7Li NMR to analyze a PEO-LiTFSI system containing $\text{Li}_{1.3}\text{Al}_{0.3}\text{Ti}_{1.7}(\text{PO}_4)_3$ (LATP) between 25 and 75 °C [13]. Coalescence between peaks corresponding to two lithiated sites in the ceramic indicated that the rate of lithium ion exchange between these

749 sites increased with temperature. [13]. The peak corresponding to LiTFSI narrowed indicating increased lithium mobility [13]. Menkin et al. used ^7Li variable temperature NMR to evaluate the impact of LiAlO_2 content on a PEO-lithium iodide (LiI) system [102]. It was found that increasing sample temperature resulted in peak narrowing between 25 and 50 °C for the peak corresponding to lithium ions in PEO and the appearance of a sharp peak (from a previously existing shoulder) at 80 °C which was assigned to the polymer-ceramic interface [102]. No changes in linewidth were observed in the peak corresponding to the bulk ceramic indicating that it did not participate in ion conduction (Figure 12) [102]. It can be seen that lineshape analysis can be particularly useful in distinguishing mobility at different sites in complex systems such as hybrid electrolytes where differences in ion dynamics between the polymer and ceramic components, as well as any interfaces, can be expected.

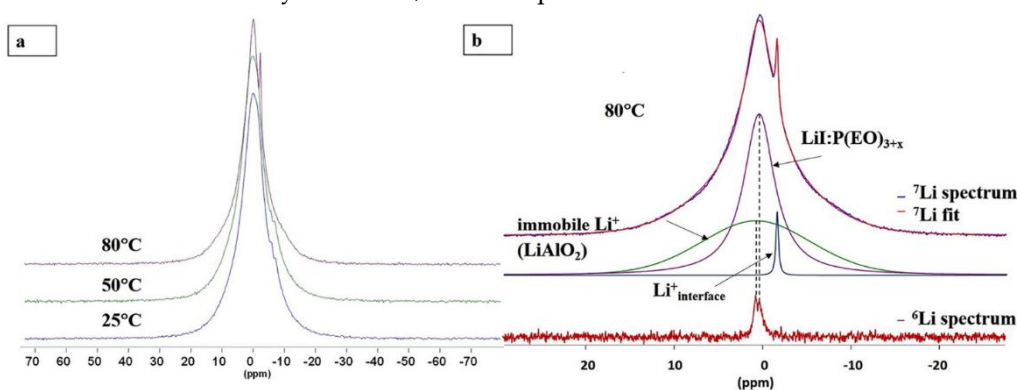

761
762 **Figure 12:** Variable temperature ^7Li NMR spectra (7.1 T, 5 kHz) of a PEO-LiI polymer matrix containing LiAlO_2 (a). Deconvolution of the spectrum at 80 °C (b). Reprinted from [102] Copyright 2019 with permission from Elsevier.

765
766 In addition to its use in variable temperature NMR, lineshape analysis has also been
767 used at constant temperatures to evaluate the effects of inert and active ceramic doping
768 on the polymer matrix in hybrid electrolyte systems [103, 104]. Xu et al. used ^1H NMR to
769 measure the hydrogen bonding interaction between a PEO- LiClO_4 polymer matrix and
770 an inert SiO_2 nanoparticle dopant in order to evaluate the effects of SiO_2 doping on PEO
771 crystallinity [103]. They found that interactions between the SiO_2 nanoparticles and the
772 polymer chain reduced crystallinity in the PEO matrix. These interactions produced
773 narrower lineshapes which indicated increased segment mobility which is typically associated
774 with increased conductivity (Figure 13) [103].

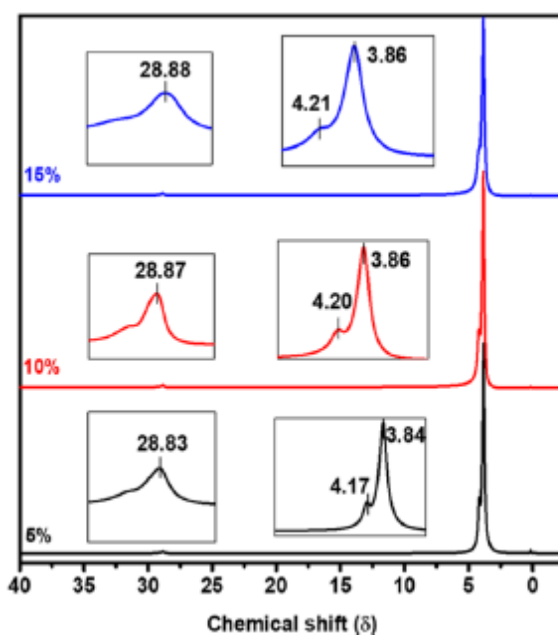


Figure 13: ^1H NMR spectra (9.4 T) of PEO-LiClO₄ membrane containing various mass percentages of SiO₂. Reprinted with permission from [103] Copyright 2020 American Chemical Society.

Conversely, Zheng and Hu, who used ^6Li NMR to analyze a PEO-LiTFSI electrolyte containing 20 and 50 wt% Li₇La₃Zr₂O₁₂ (LLZO) (an active ceramic) system, reported that increasing ceramic content increased the linewidth of the peak corresponding to the polymer as a result of decreasing crystallinity in the PEO polymer matrix [104]. As increased sample disorder may result in line broadening, the dual effects of sample disorder must be considered when evaluating NMR spectra. The types of interactions that are possible between the ceramic, either active or inert, and the polymer must therefore be well-understood to be able to determine whether changes in linewidth are indicative of changes in sample mobility or interactions between the polymer and the ceramic additive.


In addition to tracking lithium mobility, analysis of FWHM as a function of temperature was used by Lago et al. to compare the mobility of the TFSI anion in a PEO-LiTFSI electrolyte and an electrolyte system that was comprised of Al₂O₃ nanoparticles grafted to PEG and TFSI in a PEO-diglycidyl ether of poly(ethylene glycol) polymer matrix [105]. Analysis of ^{19}F FWHM revealed that the TFSI anion was significantly more mobile in the PEO-LiTFSI electrolyte than in the grafted composite electrolyte [105]. This situation is of interest as lower anion mobility serves to increase cation transference number. Line width analysis is one of the most commonly used techniques to analyze differences in mobility of sodium environments in polymer electrolytes [83, 99, 100]. Wong and Zax tracked changes in FWHM for a hybrid electrolyte comprised of PEO, lithium salt and the sodium-containing silicate montmorillonite [99]. Measuring sodium FWHM between -73 and 77 °C revealed a general decrease in linewidth with temperature which suggests that the dipolar contribution to the linewidth dominates in this system. The observation of two low temperature plateaus in a plot of sodium linewidth as a function of temperature indicates that quadrupolar interactions also contribute to the observed linewidth [99]. Work by Forsyth et al. showed that the linewidth of a poly(ethylene oxide-co-propylene-oxide) polymer electrolyte containing NaCF₃SO₃ decreased from 4.2 to 0.6 ppm between -67 and 20 °C [100]. This is indicative of increased sodium mobility in this system and suggests that dipolar contributions to the linewidth also dominate in this system. In addition to affecting FWHM, the quadrupolar interaction

809 can also cause the observed chemical shift to differ from its isotropic value. This phe-
810 nomenon was evaluated by Spindler and Shriver in a
811 poly(methyl-hydrosiloxane)-monomethyl ether poly(ethylene glycol) co-polymer that
812 contained $\text{Na}[\text{SO}_3\text{C}_3\text{F}_3]$ [106]. The ^{23}Na chemical shift was observed to become more pos-
813 itive when either sample temperature or salt content were increased [106]. This observa-
814 tion was attributed to increased interaction between cations and anions in this system.


815 2.3 Exchange Spectroscopy

816
817 Like relaxation and linewidth analysis, exchange spectroscopy (EXSY) can be used
818 to quantify changes in ion motion as a function of sample temperature or doping. EXSY is
819 typically used to identify site-specific exchange processes and provides quantitative data
820 including rates of chemical exchange and activation energies for these processes. In one
821 dimensional NMR spectra, chemical exchange is typically manifested as coalescence
822 where the approximate rate of exchange can be evaluated based on the degree of peak
823 overlap: minimal overlap indicates slow exchange, significant overlap with two sites still
824 resolvable indicates intermediate exchange and complete overlap with line narrowing
825 (motional exchange counteracts peak broadening) indicates fast exchange [107].

826 EXSY is a two dimensional NMR experiment that is generally used to analyze sys-
827 tems undergoing slow and intermediate exchange processes [107]. Slow and intermediate
828 exchange rates correspond to processes that occur prior to coalescence where the rate of
829 exchange is less than the difference in Larmor frequency between the two sites [107]. The
830 EXSY pulse sequence (Figure 14) is comprised of three 90° pulses (Table S1). The first
831 pulse frequency labels all spins in the system which are then allowed to evolve over a
832 variable delay period t_1 [108]. The second pulse inverts all spins which relax and possibly
833 undergo chemical exchange during the mixing time t_m and are observed following the
834 application of a third pulse [108]. All spins maintain the labeling that was created by the
835 first pulse which causes signals related to chemical exchange between sites to appear as
836 off-diagonal cross peaks. Off-diagonal peaks have different coordinates on each fre-
837 quency axis in the two dimensional spectrum, whereas diagonal peaks (same coordinates
838 on each axis) represent the fraction of spin which didn't undergo chemical exchange
839 (Figure 15) [108]. Multiple exchange processes are represented by multiple sets of
840 crosspeaks. Quantitative data from EXSY experiments is obtained by fitting the inte-
841 grated area of the cross peaks and the diagonal peaks. The cross peak area is normalized
842 with respect to the diagonal peak area and can be plot as a function of mixing time to
843 extract exchange rates [108]. Arrhenius plots of exchange rates can be fit to obtain activa-
844 tion energies for individual exchange processes. These activation energies are site specific
845 and can be compared to electrochemical data to determine which local exchange pro-
846 cesses do, and do not, contribute to long range conductivity. However, a disadvantage of
847 obtaining kinetic parameters via EXSY is that the experiment is time consuming since
848 two dimensional experiments must be performed at several mixing times for each tem-
849 perature to obtain reliable rates of chemical exchange.

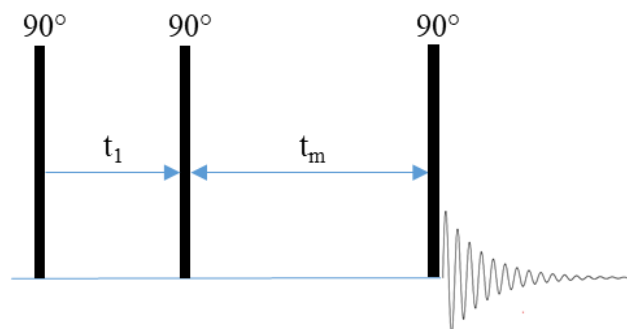

851

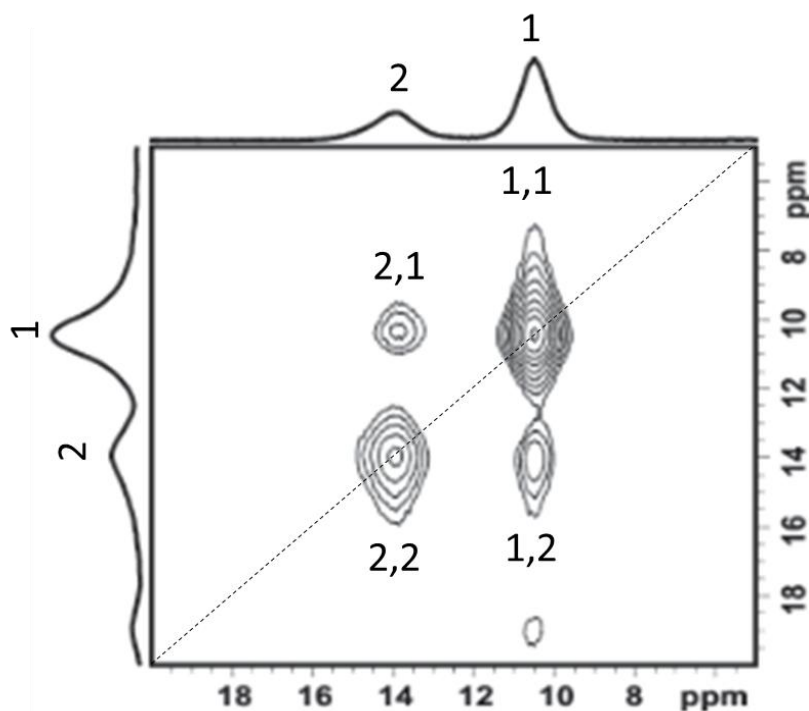Figure 14: EXSY pulse sequence.

852

853

854

855

Figure 15: Sample EXSY spectrum. Diagonal peaks (1,1 and 2,2 along the dotted line) represent the original position of each spin and have the same frequency coordinates on both axes. Cross peaks (1,2 and 2,1) represent exchanged spins and have different frequency coordinates on each axis.

856

857

858

859

860

861

862

863

864

865

866

867

868

869

870

871

872

873

874

875

876

877

878

879

A first disadvantage to using EXSY to measure chemical exchange is that the exchange rate must be equal to or greater to the spin-lattice relaxation time [109]. This limitation can result in significant constraints when ^{23}Na NMR is considered as the quadrupolar interaction in many sodium environments causes T_1 relaxation to occur more quickly relative to T_1 relaxation in ^7Li systems [47]. Chemical exchange processes that occur on a timescale that is slower than the spin-lattice relaxation cannot be observed via EXSY as crosspeaks are not produced during the mixing time, t_m in Figure 15 [109]. A second disadvantage that is relevant to the use of EXSY to analyze the chemical exchange of quadrupolar nuclei is that quadrupolar interactions typically cause line broadening as a result of second order effects not being attenuated by regular MAS spectroscopy [110]. Significant line broadening has previously been shown to obscure otherwise observable crosspeaks by decreasing peak separation and therefore increasing the minimum correlation time for a motional process to produce observable crosspeaks [111].

In the analysis of solid polymer electrolytes, EXSY has been used to demonstrate polymer mobility and to establish lithium conduction pathways in solid polymer and hybrid electrolytes. To this end, Liu et al. used ^{13}C EXSY to analyze polymer chain dynamics in a PEO-LiAsF₆ system where the impact of various molecular weights of PEO on segmental motion was evaluated [112]. Analysis of the two dimensional spectrum revealed cross peaks that were consistent with polymer chain diffusion [112]. The cross peaks that were observed between pairs of carbon atoms were consistent with forward and backward chain motion with the integrated area of the cross peaks being representative of the rate of this motion [112]. Chain diffusion was found to increase with PEO

molecular weight as it was associated with amorphous regions in the polymer matrix which remain small at low molecular weights [112].

In addition to its use in the characterization of polymers, ^7Li EXSY was also used to determine which lithiated environments are involved in ion conduction in a PEO-LiAsF₆ system that is encased in a series of α -cyclodextrin nanochannels [113]. Prior to performing the two dimensional experiment, five lithium environments were identified via one dimensional NMR techniques: Li-1 was attributed to lithium ions in PEO, Li-2 was attributed to interfacial lithium between PEO and the cyclodextrin nanochannels, Li-3 was attributed to “free” lithium ions and Li-4 and Li-5 were attributed to lithium ions in the cyclodextrin nanochannels [113]. Cross peaks were found between Li-1 and Li-2 as well as between Li-2 and Li-4 suggesting that lithium ions pass through an interfacial layer when they are transferred between PEO and the nanochannel (Figure 14) [113]. The lithium exchange rate that was calculated from the EXSY data was greater than the measured conductivity which suggests that not all local-scale motional processes contribute to long range lithium conductivity in this system [113]. However, the activation energy that was calculated via EXSY was lower than that obtained via EIS indicating additional energy barriers for long-range lithium motion in this system (Figure 16) [113]. This work demonstrates that EXSY can be used to characterize several exchange processes in a single system provided that each signal in the NMR spectrum has been previously well-characterized. It also illustrates the role that many species can play in local-scale ion motion which is not generally characterizable by electrochemical methods.


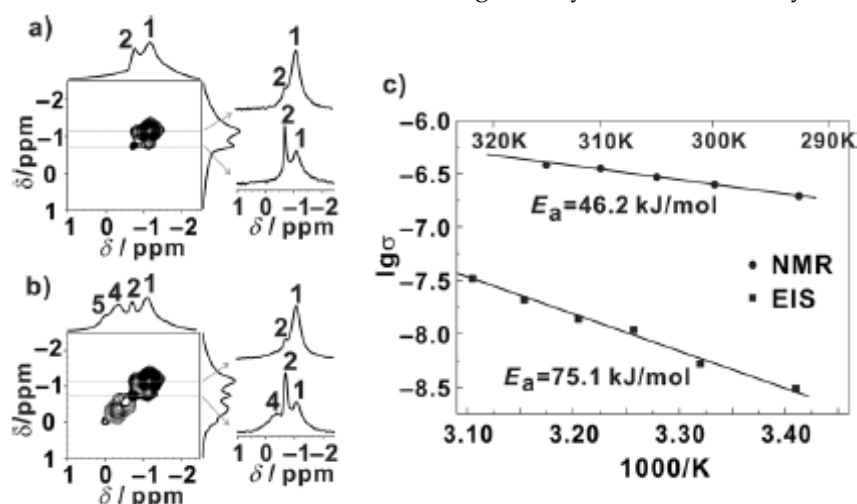


Figure 16: ^7Li EXSY spectra of PEO-LiAsF₆ in cyclodextrin nanochannels (14 T, 5 kHz MAS) with a mixing time of 300 ms. Spectrum (a) was collected with no dipolar coupling and showed correlation between the PEO and the interface. Spectrum (b) was collected with dipolar coupling where correlation between the interface and the cyclodextrin layer is observed. Activation energies calculated based on EXSY NMR data and EIS data (c). Reprinted with permission from [113] Copyright 2014 Wiley and Sons.

EXSY is not limited to homogeneous systems and, as such, was also used to measure lithium exchange between the polymer matrix and active ceramic additives in hybrid systems. Zheng et al. analyzed a PEO-LiClO₄ membrane containing LLZO, an active ceramic [114]. Their 1D ^7Li experiments identified peaks attributed to the LiClO₄ in the polymer matrix, LLZO and an interfacial layer [114]. The EXSY experiments revealed crosspeaks between the polymer and the interfacial layer [114]. No crosspeaks were observed between LLZO and the polymer or LLZO and the interface [114]. These results suggest that lithium ion conduction does not occur directly through the ceramic in this system. Conversely, the use of EXSY by Zagórski et al. to study a PEO-LiTFSI system

918 containing LLZO revealed that no interface layer is formed and that lithium ion exchange
 919 instead occurs between the ceramic and the polymer directly (Figure 17) [115]. However,
 920 electrochemical impedance spectroscopy studies that were performed on this system
 921 suggest that it is not lithium exchange between the polymer and the ceramic, but the
 922 motion of lithium ions through the polymer, that is responsible for the majority of the
 923 lithium conductivity in this system [115]. The differences in the role of the poly-
 924 mer-ceramic interface in lithium conduction pathways in these materials could be a result
 925 of differences in LLZO content. The study by Zheng et al., where an interface was ob-
 926 served, involved samples containing 50 wt% LLZO while the samples used in the work of
 927 Zagórski et al. contained 10 wt% LLZO [114, 115]. It is possible that the lower LLZO
 928 content of the samples in the latter study resulted in an insufficient quantity of interfacial
 929 lithium to detect. Additionally, lithium conduction is predicted to proceed primarily
 930 through the polymer matrix in hybrid systems with low ceramic loading [104].

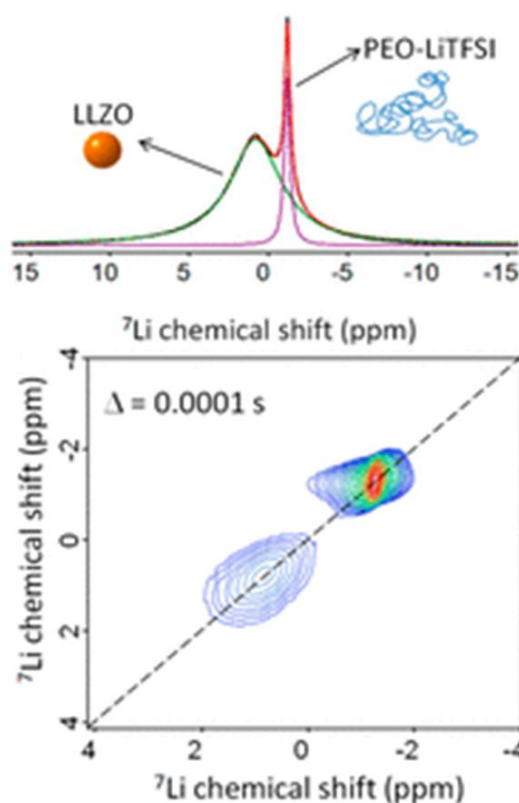

931
 932 **Figure 17:** ${}^7\text{Li}$ one dimensional and EXSY spectra (14 MHz, 20 kHz MAS) of PEO-LiTFSI containing
 933 LLZO. Reprinted with permission from [115] Copyright 2019 American Chemical Society.


934 2.4 Dipolar Coupling

935 936 2.4.1 Cross Polarization

937
 938 Like EXSY, cross polarization NMR spectroscopy (Table S1) can be used to measure
 939 correlation between chemical environments in complex systems. However, instead of
 940 relating environments based on chemical exchange, cross polarization is used to identify
 941 sites based on the strength of the heteronuclear dipolar coupling interaction that exists

942 between nuclei. The cross polarization experiment involves the transfer of magnetization
 943 from an abundant spin to a dilute spin [116]. The magnetization transfer happens as a
 944 result of the heteronuclear dipolar coupling interaction which is a distance-dependent
 945 through-space interaction that arises as a result of the interacting magnetic dipole mo-
 946 ments of proximal nuclei [117]. As a result, stronger signals are indicative of stronger
 947 dipolar couplings whereas weaker signals indicate weaker dipolar couplings. The main
 948 advantages of the technique are improved sensitivity for low abundance nuclei (up to the
 949 ratio of gyromagnetic ratios) and a reduction in experimental time as the T_1 of the
 950 abundant spin, which is generally shorter, is used during the experiment [116].

951 The cross polarization experiment (Figure 18) begins with the application of a 90°
 952 pulse on the abundant spin which is followed by a pulse that spin locks the magnetiza-
 953 tion of the abundant spin along the y-axis [116]. During this time, a pulse of same length
 954 is applied on the dilute spin which puts both magnetization vectors along the y-axis such
 955 that spin exchange can occur [116]. After the spin lock pulse, the radio frequency on the
 956 dilute spin is turned off to allow for signal acquisition while the abundant spin is de-
 957 coupled [116].

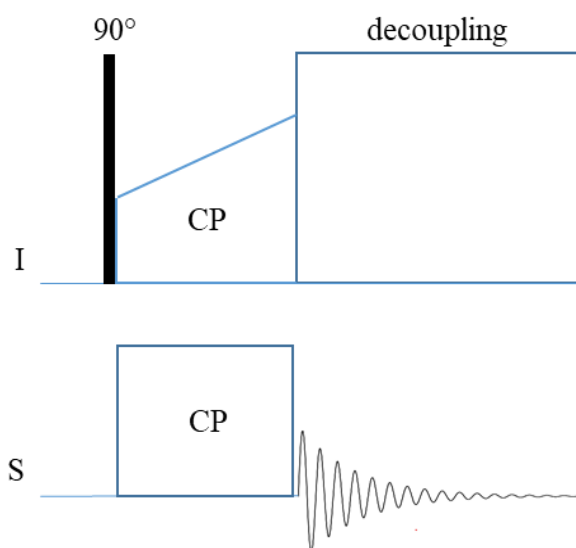

958 **Figure 18:** Cross polarization pulse sequence for the transfer of magnetization between an abun-
 959 dant spin (I) and a dilute spin (S).
 960

961 For spin exchange to occur, the Hartmann-Hahn matching condition (equation 14),
 962 where both nuclei have equal rates of precession and equal effective energies, must be
 963 met [118]. This condition is obtained by setting the effective field (B_I) on each channel
 964 such that the difference between the product of the effective magnetic field and the gy-
 965 romagnetic ratio (γ) is equal to n times the MAS rate in kilohertz where n is equal to $\pm 0, 1,$
 966 $2, \dots$
 967

$$\gamma_I B_{1I} - \gamma_S B_{1S} = nMAS \quad (14)$$

968 As magnetization transfer between spins is dependent on the strength of the dipolar
 969 coupling interaction, the resultant spectral intensities can be used to gauge distances
 970 between chemical environments (stronger signals are indicative of spin environments
 971 being closer together) and site mobility (increased motion decreases the strength of the
 972 dipolar coupling interaction).

973 Although CP NMR has yet to be used to measure sodium-ion or sodium-polymer
 974 interactions in polymer or hybrid electrolytes, it must be noted that CP NMR spectroscopy
 975 is possible between quadrupolar and non-quadrupolar nuclei as well as between
 976 two quadrupolar nuclei. In the case of cross polarization between a spin $3/2$ or $5/2$ nu-
 977 cleus and a spin $1/2$ nucleus, the Hartmann-Hahn condition (equation 14) may be satisfied

978 by matching the RF field strength of the spin $\frac{1}{2}$ nucleus to the nutation frequency of the
979 quadrupolar nucleus [119]. This condition is generally achieved by preceding the CP
980 portion of the pulse sequence with a technique used to generate multiple quantum co-
981 herence from the quadrupolar nucleus such as multiple quantum magic angle spinning
982 [119]. In the case of two quadrupolar nuclei, RF irradiation during MAS induces spin
983 state mixing which makes extremely difficult to achieve the simultaneous spin-locking
984 that is required to satisfy the Hartmann-Hahn condition (equation 14) [120]. However,
985 Puls and Eckert were able to perform ^{23}Na - ^7Li CPMAS on the mixed cation glass
986 $[(\text{Li}_2\text{O})_x(\text{Na}_2\text{O})_{1-x}]_{0.3}[\text{B}_2\text{O}_3]_{0.7}$ by first acquiring a detailed understanding of the
987 quadrupolar coupling behaviour of both nuclei by performing multiple quantum excita-
988 tion and satellite transition MAS spectroscopy prior to commencing any CPMAS ex-
989 periments [120].

990 Cross polarization NMR experiments have been performed to monitor nanochannel
991 formation in a PEO-LiAsF₆ α -cyclodextrin electrolyte systems [113, 121]. ^1H - ^{13}C cross
992 polarization experiments showed that the conformation of the glucose units in the
993 cyclodextrin changed upon nanochannel formation and was used as an indicator to
994 demonstrate that this polymer configuration was achieved [113, 121]. Additionally, in the
995 study by Yang et al., a combination of isotope labelling and cross polarization NMR was
996 used to assign lithium environments to the PEO moiety or the nanochannel [113]. This
997 was done by labeling the PEO moiety with deuterium such that the lithium environments
998 that were visible via ^2H - ^7Li cross polarization NMR could be assigned to the PEO
999 whereas environments that were visible via ^1H - ^7Li cross polarization NMR could be as-
1000 signed to the nanochannel. Lithium environments that were not observed in either ex-
1001 periment were deemed to be free lithium as larger lithium-hydrogen distances would
1002 reduce the visibility of these sites as a result of reduced dipolar coupling interactions
1003 [113]. Limited proton exchange between the nanochannel and the PEO domains was es-
1004 sential for allowing deuterium enrichment to be used as a method of distinguishing be-
1005 tween lithium environments in this system [113]. Isotope labeling experiments will be
1006 discussed in more detail in the following section.

1007 The intensity of cross polarization spectra can also be used to gauge ion mobility as
1008 increased mobility tends to reduce the strength of the dipolar coupling interaction [122].
1009 ^1H - ^{13}C cross polarization NMR has been used to compare the segmental mobilities of
1010 different polymer segments in PEG-based co-polymers. For example, in their analysis of
1011 a polystyrene PEG-methylmethacrylate co-polymer system, Daigle et al. found that the
1012 polystyrene backbone is less mobile than the PEG-methyl methacrylate sidechains as a
1013 result of the presence of attenuated peaks in a ^1H - ^{13}C cross polarization spectrum [31].
1014 However, as was determined via cross polarization NMR by Lin et al. in their analysis of
1015 a PEG-PDMS co-polymer, the mobility of the sidechain groups varied based on the de-
1016 gree of lithium salt loading [76]. Polymer side chains containing more lithium salt tended
1017 to be less mobile as a result of stronger ethylene oxide lithium salt interactions. Addi-
1018 tionally, increased sample temperature, which contributes to increased polymer mobility
1019 resulted in attenuation of the ^1H - ^{13}C cross polarization signal (Figure 19) [31]. These
1020 works show that cross polarization NMR provides enhanced characterization of a com-
1021 plex polymer system relative to what is possible with most single nucleus experiments.
1022 Additionally, cross polarization is a one-dimensional experiment meaning that a detailed
1023 characterization of the polymer structure and site interactions can be achieved more
1024 quickly than is possible using most two-dimensional techniques.

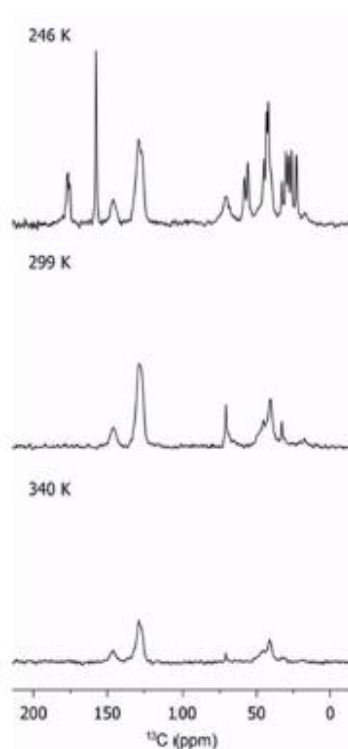


Figure 19: ^1H - ^{13}C cross polarization NMR spectra of a polystyrene PEG-methylmethacrylate co-polymer at various temperatures (9.4 T, 20 kHz MAS). Magnetochemistry 2018 [31].

2.4.2 REDOR

Rotational echo double resonance (REDOR) experiments (Table S1) are similar to cross polarization experiments in the sense that dipolar coupling interactions are used to transfer magnetization between two spins [123]. However, the REDOR experiment is generally used to provide more specific structural information as it yields site-selective dipolar coupling information for isolated spin pairs which allows internuclear distances to be determined [123, 124]. The dipolar coupling interaction, which is normally averaged out during MAS conditions, is re-introduced during the pulse sequence (Figure 20) by the application on the non-observed spin S of a train of 180° pulses that serves to invert the sign of the dipolar Hamiltonian making the average interaction non-zero [124]. The detected spin I is observed by the application of a rotor synchronized spin echo pulse sequence (Figure 20) where the 90° pulse is applied at the beginning of the experiment and the 180° pulse is applied following $2N$ rotor periods (T_r) where N is the number of cycles [123, 125].

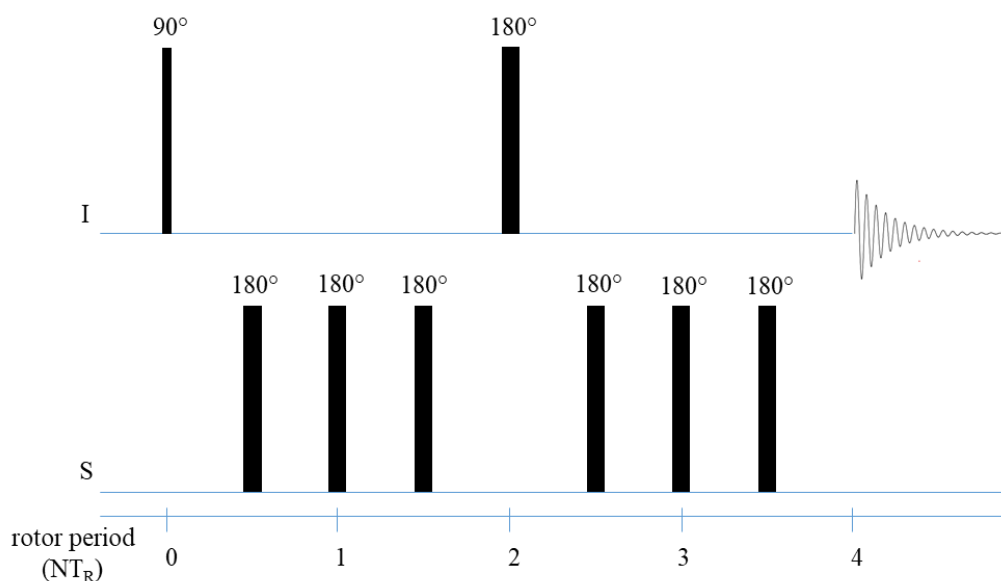


Figure 20: REDOR pulse sequence.

Dipolar coupling constants for isolated spin pairs can be extracted from REDOR spectra by plotting the ratio of the REDOR intensity (ΔS) and the normal rotational angle intensity (S_0) as a function of the dipolar evolution time as the REDOR build up curve has a universal shape in this scenario [123–125]. The intensity of the REDOR spectrum (ΔS) is expected to decrease with increasing strength of the dipolar coupling interaction. In multi-spin systems, dipolar build up curves tend to be more complex as they are influenced by the shape and geometry of the system [124, 126, 127]. However, the strength of the dipolar coupling interaction can still be approximated by fitting the early part of the REDOR build up curve before these factors have a significant influence on the shape of the curve [126, 127]. In addition, the fact that the examples that are discussed here involve dipolar coupling between protons and quadrupolar ${}^7\text{Li}$, the impact of the quadrupolar coupling interaction can also be important. However, it has been determined that the use of the pulse sequence shown in Figure 20, coupled with the low strength of the quadrupole moment in ${}^7\text{Li}$ results in the quadrupolar coupling being cancelled out as it has an equal effect on both ΔS and S_0 which allows equation 15, where I is the spin of the I spin, m is the magnetic quantum number, NT_r is the dipolar evolution time and M_2 is the second moment which can be extracted from the $\Delta S/S_0$ using a parabola fit [124].

$$\frac{\Delta S}{S_0} = \frac{1}{2I + 1} \left(\sum_{m=-I}^I (2m)^2 \right) \frac{1}{\pi^2(I + 1)I} (NT_r)^2 M_2 \quad (15)$$

Voigt and Wüllen used REDOR to assign lithium environments in polymer electrolyte samples that were comprised of PAN and LiBF_4 [128]. Two samples with differing proportions of LiBF_4 (67 wt% and 14 wt%) were analyzed. ${}^1\text{H}$ - ${}^7\text{Li}$ cross polarization spectra revealed two lithium sites, at -1.3 ppm and -2.0 ppm that were coupled to protons. As the analyzed samples were prepared by solution casting in deuterated DMSO, these sites were attributed to interactions between the lithium cations and the polymer [128]. The signal at -1.3 ppm showed no attenuation between the spin echo spectrum and the REDOR spectrum indicating limited dipolar coupling interactions. This was attributed to fast lithium motion decreasing the strength of the dipolar coupling interaction [128]. This site was therefore assigned to mobile lithium cations. The significant attenua-

tion of the signal at -2.0 ppm was observed when the spin echo spectrum was compared to the REDOR spectrum indicating stronger dipolar coupling interactions [128]. A plot of $\Delta S/S_0$ as a function of recoupling time revealed that the dipolar coupling in the sample containing 67 wt% LiBF_4 was 1.4 kHz and that the dipolar coupling in the sample containing 14 wt% LiBF_4 was 1.8 kHz indicating that having a greater percentage of PAN increases interactions between the salt and the polymer [128]. Voigt and Wüllen also performed a ^{13}C - ^7Li REDOR experiment using a PEO- LiBF_4 polymer electrolyte (36 wt % PEO and 4 wt% LiBF_4) which also contained 60 wt% succinonitrile [129]. The spin echo experiment revealed two ^{13}C signals that were correlated to lithium. One signal at 66.2 ppm exhibited a significant REDOR response and was attributed to polymer matrix containing the lithium salt [129]. The other signal at 70.7 ppm did not experience attenuation during the REDOR experiment and was attributed to an amorphous succinonitrile-based phase with little to no dipolar coupling interactions as a result of fast ion motion in the plasticized polymer [129]. As REDOR signal intensity is dependent on the strength of dipolar coupling interactions, it can be used, as shown here, to determine how changes in electrolyte composition affect polymer-salt interactions and predict subsequent ion mobilities. It is also anticipated the variable temperature REDOR experiments could be performed to determine how changes in temperature impact polymer-salt interactions and therefore ion mobility.

2.5 Isotope Enrichment

As mentioned in the ^1H - ^{13}C cross polarization analysis of PEO in cyclodextrin nanochannels performed by Yang et al., isotope enrichment can be performed to enhance other types of NMR experiments [113]. Isotope enrichment experiments are typically performed to highlight specific regions of a sample as was demonstrated above via the use of ^2H doping to distinguish hydrogen in PEO and cyclodextrin environments [113]. Since NMR spectroscopy can be performed using any isotope where the nuclear spin is greater than zero, there exists isotope enrichment options for several nuclei. The most common isotope enrichment experiment that is performed in solid polymer electrolyte research is replacing ^7Li with ^6Li . Often, these experiments are not performed using enriched samples as ^6Li has a natural abundance of 7.6 % [43]. A particular advantage of performing ^6Li NMR as opposed to ^7Li NMR is that ^6Li nuclei experience less homonuclear dipolar coupling than ^7Li nuclei as a result of its lower gyromagnetic ratio with respect to that of ^7Li (3.937 vs $10.398 \times 10^{-7} \text{ rad s}^{-1} \text{ T}^{-1}$) [43]. This results in narrower lineshapes making it easier to identify individual chemical environments in a sample. This technique was used by Zheng et al. to observe a peak attributed to a lithiated polymer-ceramic interface in a PEO- LiClO_4 sample containing LLZO particles, an active ceramic [114].

^6Li NMR is used in the analysis of solid-state polymer electrolytes to track the motional pathways of lithium in the electrolyte layer. This is done by cycling against ^6Li foils such that the regions that experience ^6Li enrichment post-cycling are identified as being a part of the lithium conduction pathway. This is because, during cycling, ^6Li ions are stripped from the foil and travel through the electrolyte. These replace existing ^7Li ions in the polymer matrix and/or ceramic and leave a trail of ^6Li -enhanced regions showing the lithium migration pathway through the electrolyte (Figure 21) [130]. The main strength of this method is that the regions involved in lithium conduction can be observed directly. However, this technique is most effective in systems where motion between domains (i.e. lithium in the polymer and lithium in the ceramic) is limited as some lithium exchange can occur under ambient conditions and would result in a slight ^6Li enrichment of the whole system.

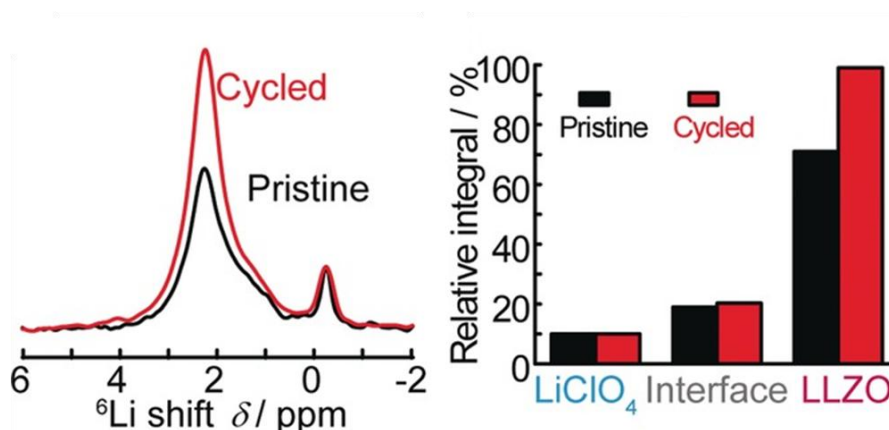


Figure 21: ^6Li foil cycling experiment performed on a PEO-LiTFSI system containing LLZO (14.1 T, 25 kHz MAS). Reprinted with permission from [130] Copyright 2014 Wiley and Sons.

This experiment has been performed by several researchers using different polymer ceramic blends [114, 131–135]. The exact conduction pathway seems to be dependent on many factors including: type of polymer used, type of ceramic used and amount of ceramic in the system. This is likely a result of the fact that it is possible for lithium to travel through the polymer only, through the interface that is produced when ceramic is introduced into a polymer matrix or through the ceramic additive only [104].

In this vein, it has been suggested that in systems which contain high quantities of ceramic, lithium conduction occurs primarily through the ceramic particles. This was observed by Zheng et al. in a PEO-LiClO₄ system containing 50 wt% LLZO, an active ceramic [114]. Yang et al. prepared polymer electrolytes from polyvinylidene fluoride-hexafluoropropylene and LiTFSI that contained 30 wt% Li_{0.33}La_{0.557}Ti_{1-x}Al_xO₃ nanowires [135]. Following cycling with ^6Li foil, the majority of the lithium signal (87.9 mol% by peak area) was located in the ceramic [135]. At lower ceramic contents, lithium conduction was observed to be more likely to occur through the interface that forms as a result of interactions between ceramic additives and the polymer matrix. In a PEO-LiTFSI system containing 25 wt% of the active ceramic LiZr₂(PO₄)₃ (LZP), it was found that the most significant ^6Li enrichment occurred in the disordered polymer environment that was believed to surround the ceramic particles [131]. Cycling a PEO-succinonitrile-LiTFSI system containing the active ceramic Li_{1+x}Al_xGe_{2-x}(PO₄)₃ (LAGP) against ^6Li foils revealed the appearance of a new lithium environment whose integrated intensity increased with increasing LAGP doping suggesting that lithium conductivity occurs through this interfacial environment [132]. It is believed that lithium conduction occurs primarily through the polymer-ceramic interface at lower levels of ceramic doping as there is not sufficient ceramic volume to form a continuous ceramic network through the sample. At even lower ceramic content, lithium conduction was found to occur primarily through the polymer matrix. This was demonstrated via a ^6Li foil cycling experiment by Xu et al. who used a PEO-LiTFSI system containing 10 wt% of the active ceramic Li_{3/8}Sr_{7/16}Zr_{1/4}O₃ (LSTZ) and Yang et al. who used a PAN-LiClO₄ system containing 5 % LLZO nanowire [133, 134]. These experiments suggest that cycling a system against an ^6Li foil is an effective way of identifying ion conduction pathways in hybrid electrolytes with various levels of ceramic loading. It is anticipated that similar results could be obtained using ^6Li -enriched ceramics as changes in spectral intensity would indicate whether/to what extent these species participate in ion transport.

3. Future Work

Despite the advantages of NMR spectroscopy for the analysis polymer and hybrid electrolytes, improvements can still be made to better characterize these materials. To this end, an additional technique, fast field cycling NMR relaxometry, in which the variance

in T_1 relaxation changes with changes in the magnetic field is used to calculate correlation times and surface diffusion associated with mobile species will be discussed here. This has had limited use in the analysis of polymer or hybrid electrolytes. However, this technique has been previously used to analyze segmental motion in polymeric materials and ion mobility in confined ionogels [136–138] and therefore has the potential to be employed in future studies in this field. These techniques can be tailored to selectively analyze specific chemical environments in a sample via sample synthesis or experimental setup allowing for even further selectivity during analysis.

Future work in the analysis of polymer and hybrid electrolytes for use in all-solid-state batteries could also focus on sodium-based batteries as the high availability and high energy density of sodium is creating increased interest in these devices. However, the higher quadrupole moment, relative to Li, can complicate the analysis of these systems by NMR spectroscopy. Future studies to investigate the ion mobility in and the molecular structure of sodium electrolytes could include NMR techniques such as multiple quantum magic angle spinning and satellite transition magic angle spinning which are specifically used to determine the number of sites present, along with their quadrupole parameters. These experiments would provide information on the nuclear environments of sodium species and inform lineshape fitting. Quadrupolar lineshape fitting could then be used to determine the impacts of electrolyte structure and external factors such as sample temperature on nuclear environments and molecular dynamics in these electrolytes.

4. Conclusions

The above examples show that solid-state NMR spectroscopy is a useful method for the analysis of molecular structure and ion dynamics in solid polymer and hybrid electrolytes. PFG NMR, which is commonly used to measure transference number in electrolyte systems, was shown to be good at characterizing local-scale ion mobility but typically worse than EIS-based measurements at describing long-range diffusion as it cannot distinguish between free ions and aggregates. Although not widely used in the analysis of solid polymer electrolytes, electrophoretic NMR is an experimentally demanding method to obtain species-specific transference numbers with accuracy that is not limited to dilute solutions. The ability of NMR based techniques to accurately describe local-scale motions that are not necessarily correlated with long-range processes can be observed in the use of variable temperature-assisted techniques for the quantification of mobility and the calculation of site-specific activation energies: T_1 relaxation, linewidth analysis and EXSY. Solid-state NMR can also be used to determine molecular structure and mobility simultaneously. This has been done via cross polarization and isotope replacement experiments. All things considered, solid-state NMR, alone or coupled with electrochemical analysis, is a powerful technique for characterizing molecular structure and ion mobility in polymer and hybrid electrolyte materials

Supplementary Materials: The following are available online at www.mdpi.com/xxx/s1, Table S1: Requirements for the analysis of solid polymer electrolytes using the NMR spectroscopy experiments that are presented in the text

Author Contributions: Conceptualization, G.F. and M.D.; writing—original draft preparation, G.F.; writing—review and editing, N.V., D.L., C.M., N.D. and M.D.; supervision, M.D.; project administration, D.L. and M.D.; funding acquisition, M.D. All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by National Sciences and Engineering Research Council of Canada (NSERC) and Total Canada Inc, NSERC Collaborative Research and Development grant number: RDCPJ 528052-18

Data Availability Statement: This study did not generate any data.

Conflicts of Interest: The authors declare no conflict of interest.

References

- Xia S, Wu X, Zhang Z, et al (2019) Practical Challenges and Future Perspectives of All-Solid-State Lithium-Metal Batteries. *Chem* 5:753–785. <https://doi.org/10.1016/j.chempr.2018.11.013>
- Kerman K, Luntz A, Viswanathan V, et al (2017) Review – Practical challenges hindering the development of solid state Li ion batteries. *J Electrochem Soc* 164:A1731–A1744. <https://doi.org/10.1149/2.1571707jes>
- Yao P, Yu H, Ding Z, et al (2019) Review on Polymer-Based Composite Electrolytes for Lithium Batteries. *Front Chem* 7:1–17. <https://doi.org/10.3389/fchem.2019.00522>
- Bucharsky EC, Schell KG, Hupfer T, et al (2016) Thermal properties and ionic conductivity of $\text{Li}_{1.3}\text{Ti}_{1.7}\text{Al}_{0.3}(\text{PO}_4)_3$ solid electrolytes sintered by field-assisted sintering. *Ionics (Kiel)* 22:1043–1049. <https://doi.org/10.1007/s11581-015-1628-3>
- Hupfer T, Bucharsky EC, Schell KG, et al (2016) Evolution of microstructure and its relation to ionic conductivity in $\text{Li}_{1+x}\text{Al}_x\text{Ti}_{2-x}(\text{PO}_4)_3$. *Solid State Ionics* 288:235–239. <https://doi.org/10.1016/j.ssi.2016.01.036>
- Hanghofer I, Gadermaier B, Wilkening A, et al (2019) Lithium ion dynamics in $\text{LiZr}_2(\text{PO}_4)_3$ and $\text{Li}_{1.4}\text{Ca}_{0.2}\text{Zr}_{1.8}(\text{PO}_4)_3$. *Dalt Trans* 48:9376–9387. <https://doi.org/10.1039/c9dt01786k>
- Li W, Sun C, Jin J, et al (2019) Realization of the Li + domain diffusion effect via constructing molecular brushes on the LLZTO surface and its application in all-solid-state lithium batteries. *J Mater Chem A* 7:27304–27312. <https://doi.org/10.1039/c9ta10400c>
- Kato Y, Hori S, Saito T, et al (2016) High-power all-solid-state batteries using sulfide superionic conductors. *Nat Energy* 1:1–7. <https://doi.org/10.1038/nenergy.2016.30>
- Epp V, Ma Q, Hammer EM, et al (2015) Very fast bulk Li ion diffusivity in crystalline $\text{Li}_{1.5}\text{Al}_{0.5}\text{Ti}_{1.5}(\text{PO}_4)_3$ as seen using NMR relaxometry. *Phys Chem Chem Phys* 17:32115–32121. <https://doi.org/10.1039/c5cp05337d>
- Yu X, Manthiram A (2020) A Long-cycle-life All-solid-state Lithium Battery with a Ceramic-polymer Composite Electrolyte. *ACS Appl Energy Mater*. <https://doi.org/10.1021/acsaem.9b02547>
- Tominaga Y, Yamazaki K, Nanthana V (2015) Effect of anions on lithium ion conduction in poly(ethylene carbonate)-based polymer electrolytes. *J Electrochem Soc* 162:A3133–A3136. <https://doi.org/10.1149/2.0211502jes>
- Chen L, Li Y, Li SP, et al (2018) PEO/garnet composite electrolytes for solid-state lithium batteries: From “ceramic-in-polymer” to “polymer-in-ceramic.” *Nano Energy* 46:176–184. <https://doi.org/10.1016/j.nanoen.2017.12.037>
- Bonizzoni S, Ferrara C, Berbenni V, et al (2019) NASICON-type polymer-in-ceramic composite electrolytes for lithium batteries. *Phys Chem Chem Phys* 21:6142–6149. <https://doi.org/10.1039/c9cp00405j>
- Yan C, Zhu P, Jia H, et al (2020) Garnet-rich composite solid electrolytes for dendrite-free, high-rate, solid-state

- 1249 lithium-metal batteries. *Energy Storage Mater* 26:448–456. <https://doi.org/10.1016/j.ensm.2019.11.018>
- 1250 15. Liu W, Lee SW, Lin D, et al (2017) Enhancing ionic conductivity in composite polymer electrolytes with well-aligned
1251 ceramic nanowires. *Nat Energy* 2:17035. <https://doi.org/10.1038/nenergy.2017.35>
- 1252 16. Boaretto N, Meabe L, Martinez-Ibañez M, et al (2020) Review—Polymer Electrolytes for Rechargeable Batteries: From
1253 Nanocomposite to Nanohybrid. *J Electrochem Soc* 167:070524. <https://doi.org/10.1149/1945-7111/ab7221>
- 1254 17. Liang M, Liu Y, Xiao B, et al (2018) An analytical model for the transverse permeability of gas diffusion layer with electrical
1255 double layer effects in proton exchange membrane fuel cells. *Int J Hydrogen Energy* 43:17880–17888.
1256 <https://doi.org/10.1016/j.ijhydene.2018.07.186>
- 1257 18. Liang M, Fu C, Xiao B, et al (2019) A fractal study for the effective electrolyte diffusion through charged porous media. *Int J*
1258 *Heat Mass Transf* 137:365–371. <https://doi.org/10.1016/j.ijheatmasstransfer.2019.03.141>
- 1259 19. West K, Zachau-Christiansen B, Jacobsen T, et al (1988) Poly(Ethylene Oxide)-Sodium Perchlorate Electrolytes in
1260 Solid-State Sodium Cells. *Br Polym J* 20:243–246. <https://doi.org/10.1002/pi.4980200315>
- 1261 20. Wang Y, Song S, Xu C, et al (2019) Development of solid-state electrolytes for sodium-ion battery—A short review. *Nano*
1262 *Mater Sci* 1:91–100. <https://doi.org/10.1016/j.nanoms.2019.02.007>
- 1263 21. Colò F, Bella F, Nair JR, et al (2015) Cellulose-based novel hybrid polymer electrolytes for green and efficient Na-ion
1264 batteries. *Electrochim Acta* 174:185–190. <https://doi.org/10.1016/j.electacta.2015.05.178>
- 1265 22. Hashmi SA, Chandra S (1995) Experimental investigations on a sodium-ion-conducting polymer electrolyte based on
1266 poly(ethylene oxide) complexed with NaPF₆. *Mater Sci Eng B* 34:18–26. [https://doi.org/10.1016/0921-5107\(95\)01219-2](https://doi.org/10.1016/0921-5107(95)01219-2)
- 1267 23. Luo H, Liang X, Wang L, et al (2014) Highly mobile segments in crystalline poly(ethylene oxide) 8:NaPF₆ electrolytes
1268 studied by solid-state NMR spectroscopy. *J Chem Phys* 140:. <https://doi.org/10.1063/1.4865109>
- 1269 24. Guo M, Zhang M, He D, et al (2017) Comb-like solid polymer electrolyte based on polyethylene glycol-grafted sulfonated
1270 polyether ether ketone. *Electrochim Acta* 255:396–404. <https://doi.org/10.1016/j.electacta.2017.10.033>
- 1271 25. Bhide A, Hariharan K (2008) Composite polymer electrolyte based on (PEO)₆:NaPO₃ dispersed with BaTiO₃. *Polym Int*
1272 57:523–529. <https://doi.org/10.1002/pi>
- 1273 26. Zhang Q, Liu K, Ding F, Liu X (2017) Recent advances in solid polymer electrolytes for lithium batteries. *Nano Res*
1274 10:4139–4174. <https://doi.org/10.1007/s12274-017-1763-4>
- 1275 27. Xu K (2014) Electrolytes and interphases in Li-ion batteries and beyond. *Chem Rev* 114:11503–11618.
1276 <https://doi.org/10.1021/cr500003w>
- 1277 28. Pecher O, Carretero-Gonzalez J, Griffith KJ, Grey CP (2017) Materials' methods: NMR in battery research. *Chem Mater*
1278 29:213–242. <https://doi.org/10.1021/acs.chemmater.6b03183>
- 1279 29. Keeler J (2002) *Understanding NMR Spectroscopy*, second. Cambridge University Press, Cambridge, UK
- 1280 30. Roach DJ, Dou S, Colby RH, Mueller KT (2012) Nuclear magnetic resonance investigation of dynamics in poly(ethylene
1281 oxide)-based lithium polyether-ester-sulfonate ionomers. *J Chem Phys* 136:014510. <https://doi.org/10.1063/1.3669449>
- 1282 31. Daigle J-C, Arnold A, Vijn A, Zaghbi K (2018) Solid-State NMR Study of New Copolymers as Solid Polymer Electrolytes.

- 1283 Magnetochemistry 4:13. <https://doi.org/10.3390/magnetochemistry4010013>
- 1284 32. Morales DJ, Greenbaum S (2020) NMR Investigations of Crystalline and Glassy Solid Electrolytes for Lithium Batteries: A
1285 Brief Review. *Int J Mol Sci* 21:3402. <https://doi.org/10.3390/ijms21093402>
- 1286 33. Zujovic Z, Kilmartin PA, Travas-sejdic J (2020) The Applications of Solid-State NMR to Conducting Polymers . The Special
1287 Case on Polyaniline. *Molecules* 25:444
- 1288 34. Abbrent S, Greenbaum SG (2010) Using nuclear magnetic resonance spectroscopy in polymer electrolyte research. In:
1289 *Polymer Electrolytes Fundamentals and Applications*. Woodhead publishing series in electronic and optical materials, pp
1290 278–313
- 1291 35. Price W (1997) Pulsed-Field Gradient Nuclear Magnetic Resonance as a Tool for Studying Translational Diffusion: Part 1.
1292 Basic Theory. pp 299–336
- 1293 36. Sun B, Mindemark J, Morozov E V., et al (2016) Ion transport in polycarbonate based solid polymer electrolytes:
1294 Experimental and computational investigations. *Phys Chem Chem Phys* 18:9504–9513. <https://doi.org/10.1039/c6cp00757k>
- 1295 37. Liu X, Ding G, Zhou X, et al (2017) An interpenetrating network poly(diethylene glycol carbonate)-based polymer
1296 electrolyte for solid state lithium batteries. *J Mater Chem A* 5:11124–11130. <https://doi.org/10.1039/c7ta02423a>
- 1297 38. Shah FU, Gnezdilov OI, Gusain R, Filippov A (2017) Transport and Association of Ions in Lithium Battery Electrolytes
1298 Based on Glycol Ether Mixed with Halogen-Free Orthoborate Ionic Liquid. *Sci Rep* 7:1–13.
1299 <https://doi.org/10.1038/s41598-017-16597-7>
- 1300 39. Stejskal EO, Tanner JE (1965) Spin diffusion measurements: Spin echoes in the presence of a time-dependent field gradient.
1301 *J Chem Phys* 42:288–292. <https://doi.org/10.1063/1.1695690>
- 1302 40. Cotts RM, Hoch MJR, Sun T, Markert JT (1989) Pulsed field gradient stimulated echo methods for improved NMR diffusion
1303 measurements in heterogeneous systems. *J Magn Reson* 83:252–266. [https://doi.org/10.1016/0022-2364\(89\)90189-3](https://doi.org/10.1016/0022-2364(89)90189-3)
- 1304 41. Tanner JE (1970) Use of the stimulated echo in nmr diffusion studies. *J Chem Phys* 52:2523–2526.
1305 <https://doi.org/10.1063/1.1673336>
- 1306 42. Engelke S, Marbella LE, Trease NM, et al (2019) Three-dimensional pulsed field gradient NMR measurements of
1307 self-diffusion in anisotropic materials for energy storage applications. *Phys Chem Chem Phys* 21:4538–4546.
1308 <https://doi.org/10.1039/c8cp07776b>
- 1309 43. Harris RK, Becker ED, Goodfellow R, Granger P (2002) NMR nomenclature: nuclear spin properties and conventions for
1310 chemical shifts. IUPAC recommendations 2001. *Magn Reson Chem* 40:489–505. <https://doi.org/10.1002/mrc.1042>
- 1311 44. Adebahr J, Best AS, Byrne N, et al (2003) Ion transport in polymer electrolytes containing nanoparticulate TiO₂: The
1312 influence of polymer morphology. *Phys Chem Chem Phys* 5:720–725. <https://doi.org/10.1039/b208454f>
- 1313 45. Hosseinioun A, Nürnberg P, Schönhoff M, et al (2019) Improved lithium ion dynamics in crosslinked PMMA gel polymer
1314 electrolyte. *RSC Adv* 9:27574–27582. <https://doi.org/10.1039/c9ra05917b>
- 1315 46. Foran G, Mankovsky D, Verdier N, et al (2020) The Impact of Absorbed Solvent on the Performance of Solid Polymer
1316 Electrolytes for Use in Solid-State Lithium Batteries. *iScience* 23

- 1317 47. Greenbaum SG (1993) NMR studies of ion mobility and association in polyether-based polymer electrolytes. *Polym Adv*
1318 *Technol* 4:172–178. <https://doi.org/10.1002/pat.1993.220040217>
- 1319 48. Yang L, Jiang Y, Liang X, et al (2020) Novel sodium–poly(tartaric acid)borate-based single-ion conducting polymer
1320 electrolyte for sodium–metal batteries. *ACS Appl Energy Mater* 3:10053–10060. <https://doi.org/10.1021/acsaem.0c01756>
- 1321 49. Verdier N, Lepage D, Zidani R, et al (2020) Crosslinked polyacrylonitrile-based elastomer used as gel polymer electrolyte
1322 in Li-ion battery applications. *Appl Energy Mater* 3:1099–1110. <https://doi.org/10.1021/acsaem.9b02129>
- 1323 50. Fong KD, Self J, Diederichsen KM, et al (2019) Ion Transport and the True Transference Number in Nonaqueous
1324 Polyelectrolyte Solutions for Lithium Ion Batteries. *ACS Cent Sci* 5:1250–1260. <https://doi.org/10.1021/acscentsci.9b00406>
- 1325 51. Mindemark J, Lacey MJ, Bowden T, Brandell D (2018) Beyond PEO—Alternative host materials for Li⁺-conducting solid
1326 polymer electrolytes. *Prog Polym Sci* 81:114–143. <https://doi.org/10.1016/j.progpolymsci.2017.12.004>
- 1327 52. Evans J, Vincent CA, Bruce PG (1987) Electrochemical measurement of transference numbers in polymer electrolytes.
1328 *Polymer (Guildf)* 28:2324–2328. [https://doi.org/10.1016/0032-3861\(87\)90394-6](https://doi.org/10.1016/0032-3861(87)90394-6)
- 1329 53. Pesko DM, Timachova K, Bhattacharya R, et al (2017) Negative Transference Numbers in Poly(ethylene oxide)-Based
1330 Electrolytes. *J Electrochem Soc* 164:E3569–E3575. <https://doi.org/10.1149/2.0581711jes>
- 1331 54. Balsara NP, Newman J (2015) Relationship between Steady-State Current in Symmetric Cells and Transference Number of
1332 Electrolytes Comprising Univalent and Multivalent Ions. *J Electrochem Soc* 162:A2720–A2722.
1333 <https://doi.org/10.1149/2.0651514jes>
- 1334 55. Pesko D (2018) Complete Electrochemical Characterization of Ion Transport in Polymer Electrolytes. University of
1335 California, Berkeley
- 1336 56. Hittorf W (1853) Ueber die Wanderungen der Ionen Während der Electrolyse. *Ann Phys* 165:177–211.
1337 <https://doi.org/http://doi.org/10.1002/andp.18531650602>
- 1338 57. Bruce PG, Hardgrave MT, Vincent CA (1992) The determination of transference numbers in solid polymer electrolytes
1339 using the Hittorf method. *Solid State Ionics* 53–56:1087–1094. [https://doi.org/10.1016/0167-2738\(92\)90295-Z](https://doi.org/10.1016/0167-2738(92)90295-Z)
- 1340 58. Kaneko F, Wada S, Nakayama M, et al (2009) Dynamic transport in li-conductive polymer electrolytes plasticized with
1341 poly(ethylene glycol)-borate/aluminate ester. *ChemPhysChem* 10:1911–1915. <https://doi.org/10.1002/cphc.200900191>
- 1342 59. Chintapalli M, Timachova K, Olson KR, et al (2016) Relationship between Conductivity, Ion Diffusion, and Transference
1343 Number in Perfluoropolyether Electrolytes. *Macromolecules* 49:3508–3515. <https://doi.org/10.1021/acs.macromol.6b00412>
- 1344 60. Tominaga Y, Yamazaki K (2014) Fast Li-ion conduction in poly(ethylene carbonate)-based electrolytes and composites
1345 filled with TiO₂ nanoparticles. *Chem Commun* 50:4448–4450. <https://doi.org/10.1039/c3cc49588d>
- 1346 61. Timachova K, Sethi GK, Bhattacharya R, et al (2019) Ion diffusion across a disorder-to-order phase transition in a
1347 poly(ethylene oxide)-*b*-poly(silsesquioxane) block copolymer electrolyte. *Mol Syst Des Eng* 4:357–364.
1348 <https://doi.org/10.1039/c8me00077h>
- 1349 62. Cheung IW, Chin KB, Greene ER, et al (2003) Electrochemical and solid state NMR characterization of composite
1350 PEO-based polymer electrolytes. *Electrochim Acta* 48:2149–2156. [https://doi.org/10.1016/S0013-4686\(03\)00198-1](https://doi.org/10.1016/S0013-4686(03)00198-1)

- 1351 63. Bhattacharja S, Smoot SW, Whitmore DH (1986) Cation and Anion Diffusion in the Amorphous Phase of the Polymer
1352 Electrolyte (PEO)₈LiCf₃SO₃. *Solid State Ionics* 18–19:306–314. <https://doi.org/10.1017/CBO9781107415324.004>
- 1353 64. Gorecki W, Donoso P, Berthier C, et al (1988) NMR, DSC and conductivity study of the polymer solid electrolytes P(EO)
1354 (LiCp+1F₂p+3SO₃)_x. *Solid State Ionics* 28–30:1018–1022. [https://doi.org/10.1016/0167-2738\(88\)90323-2](https://doi.org/10.1016/0167-2738(88)90323-2)
- 1355 65. Al-Salih H, Huang A, Yim C-H, et al (2020) A Polymer-Rich Quaternary Composite Solid Electrolyte for Lithium Batteries. *J*
1356 *Electrochem Soc* 167:070557. <https://doi.org/10.1149/1945-7111/ab7fb8>
- 1357 66. Zhang Z, Madsen LA (2014) Observation of separate cation and anion electrophoretic mobilities in pure ionic liquids. *J*
1358 *Chem Phys* 140:. <https://doi.org/10.1063/1.4865834>
- 1359 67. Stilbs P, Furó I (2006) Electrophoretic NMR. *Curr Opin Colloid Interface Sci* 11:3–6.
1360 <https://doi.org/10.1016/j.cocis.2005.09.016>
- 1361 68. Pettersson E, Furó I, Stilbs P (2004) On experimental aspects of electrophoretic NMR. *Concepts Magn Reson Part A Bridg*
1362 *Educ Res* 22:61–68. <https://doi.org/10.1002/cmr.a.20012>
- 1363 69. Rosenwinkel MP, Schönhoff M (2019) Lithium Transference Numbers in PEO/LiTFSa Electrolytes Determined by
1364 Electrophoretic NMR. *J Electrochem Soc* 166:A1977–A1983. <https://doi.org/10.1149/2.0831910jes>
- 1365 70. Harris RK (1983) *Nuclear Magnetic Resonance Spectroscopy*. Pitman Publishing INC, Marshfield, Massachusetts
- 1366 71. Foerster H, Struppe J, Steuernager S, et al (2009) *Solid State NMR AVANCE Solids User Manual*
- 1367 72. Jeon JD, Kwak SY (2006) Variable-temperature ⁷Li solid-state NMR investigation of Li-ion mobility and its correlation with
1368 conductivity in pore-filling polymer electrolytes for secondary batteries. *Macromolecules* 39:8027–8034.
1369 <https://doi.org/10.1021/ma061521v>
- 1370 73. Abragam A (1961) *The Principles pf Nuclear Magnetism*. Clarendon Press
- 1371 74. Stone NJ (2001) *Table of nuclear magnetic dipole and electric quadrupole moments*
- 1372 75. Kentgens APM (1997) A practival guide to solid-state NMR of half-integer quadrupolar nuclei with some applications to
1373 disordered systems. *Geoderma* 80:271–306
- 1374 76. Lin CL, Kao HM, Wu RR, Kuo PL (2002) Multinuclear solid-state NMR, DSC, and conductivity studies of solid polymer
1375 electrolytes based on polyurethane/poly(dimethylsiloxane) segmented copolymers. *Macromolecules* 35:3083–3096.
1376 <https://doi.org/10.1021/ma012012q>
- 1377 77. Stallworth PE, Greenbaum SG, Croce F, et al (1995) Lithium-7 NMR and ionic conductivity studies of gel electrolytes based
1378 on poly(methylmethacrylate). *Electrochim Acta* 40:2137–2141. [https://doi.org/10.1016/0013-4686\(95\)00153-6](https://doi.org/10.1016/0013-4686(95)00153-6)
- 1379 78. Kumar B, Marsh R (1991) *Polymer Batteries*. SAE Trans 100:408–412
- 1380 79. Chen-Yang YW, Chen HC, Lin FJ, Chen CC (2002) Polyacrylonitrile electrolytes: 1. A novel high-conductivity composite
1381 polymer electrolyte based on PAN, LiClO₄ and α-Al₂O₃. *Solid State Ionics* 150:327–335.
1382 [https://doi.org/10.1016/S0167-2738\(02\)00457-5](https://doi.org/10.1016/S0167-2738(02)00457-5)
- 1383 80. Diederichsen KM, Buss HG, McCloskey BD (2017) The Compensation Effect in the Vogel-Tammann-Fulcher (VTF)
1384 Equation for Polymer-Based Electrolytes. *Macromolecules* 50:3831–3840. <https://doi.org/10.1021/acs.macromol.7b00423>

- 1385 81. Keeler J (2004) Chapter 8. Relaxation. http://www-keeler.ch.cam.ac.uk/lectures/understanding/chapter_8.pdf. Accessed 26
1386 Feb 2019
- 1387 82. Peng J, Xiao Y, Clarkson DA, et al (2020) A Nuclear Magnetic Resonance Study of Cation and Anion Dynamics in
1388 Polymer–Ceramic Composite Solid Electrolytes. *ACS Appl Polym Mater* 2:1180–1189.
1389 <https://doi.org/10.1021/acsapm.9b01068>
- 1390 83. Schantz S, Kakihana M (1990) NMR study of a poly(propylene oxide)-NaCF₃SO₃ polymer electrolyte. *Solid State Ionics*
1391 40–41:645–647. <https://doi.org/10.1515/znb-1965-0902>
- 1392 84. Pak YS, Adamic KJ, Greenbaum SG, et al (1991) Complex impedance and multifrequency ²³Na NMR study of poly
1393 (propylene oxide) complexed with NaB(C₆H₅)₄. *Solid State Ionics* 45:277–284. [https://doi.org/10.1016/0167-2738\(91\)90162-5](https://doi.org/10.1016/0167-2738(91)90162-5)
- 1394 85. Daigle J-C, Arnold A, Vijh A, Zaghib K (2018) Solid-State NMR Study of New Copolymers as Solid Polymer Electrolytes.
1395 *Magnetochemistry* 4:13. <https://doi.org/10.3390/magnetochemistry4010013>
- 1396 86. Forsyth M, MacFarlane DR, Meakin P, et al (1995) An nmr investigation of ionic structure and mobility in plasticized solid
1397 polymer electrolytes. *Electrochim Acta* 40:2343–2347. [https://doi.org/10.1016/0013-4686\(95\)00190-P](https://doi.org/10.1016/0013-4686(95)00190-P)
- 1398 87. Atta-ur-Rahman, Choudhary MI, Atia-tul-Wahab (2016) Spin-Echo and Polarization Transfer. In: *Solving Problems with*
1399 *NMR Spectroscopy*, second. Academic Press, pp 133–190
- 1400 88. Forsyth M, Jiazeng S, MacFarlane DR (2000) Novel high salt content polymer electrolytes based on high T_g polymers.
1401 *Electrochim Acta* 45:1249–1254. [https://doi.org/10.1016/S0013-4686\(99\)00328-X](https://doi.org/10.1016/S0013-4686(99)00328-X)
- 1402 89. Carr HY, Purcell EM (1954) Effects of diffusion on free precession in nuclear magnetic resonance experiments. *Phys Rev*
1403 94:630–638. <https://doi.org/10.1103/PhysRev.94.630>
- 1404 90. Meiboom S, Gill D (1958) Modified spin-echo method for measuring nuclear relaxation times. *Rev Sci Instrum* 29:688–691.
1405 <https://doi.org/10.1063/1.1716296>
- 1406 91. Donoso JP, Cavalcante MG, Bonagamba TJ, et al (1995) Magnetic resonance study of water absorption in some peo-lithium
1407 salt polymer electrolytes. *Electrochim Acta* 40:2357–2360. [https://doi.org/10.1016/0013-4686\(95\)00193-I](https://doi.org/10.1016/0013-4686(95)00193-I)
- 1408 92. Franco RWA, Donoso JP, Magon CJ, et al (2000) NMR and DSC study of polymer electrolyte-Carbon Black composites.
1409 *Solid State Ionics* 136–137:1181–1187. [https://doi.org/10.1016/S0167-2738\(00\)00582-8](https://doi.org/10.1016/S0167-2738(00)00582-8)
- 1410 93. Kwak GH, Tominaga Y, Asai S, Sumita M (2003) Effect of reaction kinetics of polymer electrolyte on the ion-conductive
1411 behavior for poly(oligo oxyethylene methacrylate)-LiTFSI mixtures. *J Appl Polym Sci* 89:2149–2156.
1412 <https://doi.org/10.1002/app.12375>
- 1413 94. Kidd BE, Forbey SJ, Steuber FW, et al (2015) Multiscale Lithium and Counterion Transport in an Electrospun Polymer-Gel
1414 Electrolyte. *Macromolecules* 48:4481–4490. <https://doi.org/10.1021/acs.macromol.5b00573>
- 1415 95. Huang B, Wang Z, Chen L, et al (1996) The Mechanism of Lithium Ion Transport in Polyacrylonitrile-Based Polymer
1416 Electrolytes. *Solid State Ionics* 91:279–284. [https://doi.org/10.1016/0921-5107\(89\)90175-X](https://doi.org/10.1016/0921-5107(89)90175-X)
- 1417 96. Chung SH, Wang Y, Persi L, et al (2001) Enhancement of ion transport in polymer electrolytes by addition of nanoscale
1418 inorganic oxides. *J Power Sources* 97–98:644–648. [https://doi.org/10.1016/S0378-7753\(01\)00748-0](https://doi.org/10.1016/S0378-7753(01)00748-0)

- 1419 97. Liu TM, Saikia D, Ho SY, et al (2017) High ion-conducting solid polymer electrolytes based on blending hybrids derived
1420 from monoamine and diamine polyethers for lithium solid-state batteries. *RSC Adv* 7:20373–20383.
1421 <https://doi.org/10.1039/c7ra01542a>
- 1422 98. Munoz S, Greenbaum S (2018) Review of recent nuclear magnetic resonance studies of ion transport in polymer electrolytes.
1423 *Membranes (Basel)* 8:1–23. <https://doi.org/10.3390/membranes8040120>
- 1424 99. Wong S, Zax DB (1997) What do NMR linewidths tell us? Dynamics of alkali cations in a PEO-based nanocomposite
1425 polymer electrolyte. *Electrochim Acta* 42:3513–3518. [https://doi.org/10.1016/S0013-4686\(97\)00040-6](https://doi.org/10.1016/S0013-4686(97)00040-6)
- 1426 100. Forsyth M, Smith ME, Meakin P, MacFarlane DR (1994) ²³Na NMR in urethane cross-linked polyether solid polymer
1427 electrolytes. *J Polym Sci Part B Polym Phys* 32:2077–2084. <https://doi.org/10.1002/polb.1994.090321214>
- 1428 101. Berman MB, Greenbaum SG (2015) NMR studies of solvent-free ceramic composite polymer electrolytes—A brief review.
1429 *Membranes (Basel)* 5:915–923. <https://doi.org/10.3390/membranes5040915>
- 1430 102. Menkin S, Lifshitz M, Haimovich A, et al (2019) Evaluation of ion-transport in composite polymer-in-ceramic electrolytes.
1431 Case study of active and inert ceramics. *Electrochim Acta* 304:447–455. <https://doi.org/10.1016/j.electacta.2019.03.006>
- 1432 103. Xu Z, Yang T, Chu X, et al (2020) Strong Lewis Acid-base and Weak Hydrogen Bond Synergistically Enhancing Ionic
1433 Conductivity of Poly (ethylene oxide)@ SiO₂ Electrolytes for High Rate-capability Li-metal Battery. *ACS Appl Mater*
1434 *Interfaces* 12:10341–10329. <https://doi.org/10.1021/acsami.9b20128>
- 1435 104. Zheng J, Hu YY (2018) New Insights into the Compositional Dependence of Li-Ion Transport in Polymer-Ceramic
1436 Composite Electrolytes. *ACS Appl Mater Interfaces* 10:4113–4120. <https://doi.org/10.1021/acsami.7b17301>
- 1437 105. Lago N, Garcia-Calvo O, Lopezdelamo JM, et al (2015) All-Solid-State Lithium-Ion Batteries with Grafted Ceramic
1438 Nanoparticles Dispersed in Solid Polymer Electrolytes. *ChemSusChem* 8:3039–3043. <https://doi.org/10.1002/cssc.201500783>
- 1439 106. Spindler R, Shriver DF (1988) Investigations of a Siloxane-Based Polymer Electrolyte Employing ¹³C, ²⁹Si, ⁷Li, and ²³Na
1440 Solid-State NMR Spectroscopy. *J Am Chem Soc* 110:3036–3043. <https://doi.org/10.1021/ja00218a006>
- 1441 107. Bain AD (2003) Chemical exchange in NMR. *Prog Nucl Magn Reson Spectrosc* 43:63–103.
1442 <https://doi.org/10.1016/j.pnmrs.2003.08.001>
- 1443 108. Bain AD (2008) Chemical Exchange. *Annu Reports NMR Spectrosc* 63:23–48. [https://doi.org/10.1016/S0066-4103\(07\)63002-6](https://doi.org/10.1016/S0066-4103(07)63002-6)
- 1444 109. Smiley DL, Goward GR (2016) Ex Situ ²³Na Solid-State NMR Reveals the Local Na-Ion Distribution in Carbon-Coated
1445 Na₂FePO₄F during Electrochemical Cycling. *Chem Mater* 28:7645–7656. <https://doi.org/10.1021/acs.chemmater.6b02539>
- 1446 110. Autschbach J, Zheng S, Schurko, Robert W (2010) Analysis of Electric Field Gradient Tensors at Quadrupolar Nuclei in
1447 Common Structural Motifs. *Concepts Magn Reson A* 36:84–126. <https://doi.org/10.1002/cmr.a.20155>
- 1448 111. Foran GY, Goward GR Site-Specific Proton Dynamics in Indium-Doped Tin Pyrophosphate Published as part of The
1449 *Journal of Physical Chemistry virtual special issue “ Hellmut Eckert Festschrift ”*. *J Phys Chem C*.
1450 <https://doi.org/10.1021/acs.jpcc.0c09290>
- 1451 112. Liu Q, Li C, Wei L, et al (2014) The phase structure, chain diffusion motion and local reorientation motion: ¹³C Solid-state
1452 NMR study on the highly-crystalline solid polymer electrolytes. *Polymer (Guildf)* 55:5454–5459.
1453 <https://doi.org/10.1016/j.polymer.2014.08.055>

- 1454 113. Yang LY, Wei DX, Xu M, et al (2014) Transferring lithium ions in nanochannels: A PEO/Li⁺ solid polymer electrolyte
1455 design. *Angew Chemie - Int Ed* 53:3631–3635. <https://doi.org/10.1002/anie.201307423>
- 1456 114. Zheng J, Tang M, Hu Y-Y (2016) Lithium Ion Pathway within Li₇La₃Zr₂O₁₂-Polyethylene Oxide Composite
1457 Electrolytes. *Angew Chemie* 128:12726–12730. <https://doi.org/10.1002/ange.201607539>
- 1458 115. Zagórski J, López Del Amo JM, Cordill MJ, et al (2019) Garnet-Polymer Composite Electrolytes: New Insights on Local
1459 Li-Ion Dynamics and Electrodeposition Stability with Li Metal Anodes. *ACS Appl Energy Mater* 2:1734–1746.
1460 <https://doi.org/10.1021/acsaem.8b01850>
- 1461 116. Kolodziejski W, Klinowski J (2002) Kinetics of Cross-Polarization in Solid-State NMR: A Guide for Chemists. *Chem Rev*
1462 102:613–628. <https://doi.org/10.1021/cr000060n>
- 1463 117. Levitt MH (2008) *Spin Dynamics: Basics of Nuclear Magnetic Resonance*, second. John Wiley & Sons
- 1464 118. Hartmann SR, Hahn EL (1962) Nuclear double resonance in the rotating frame. *Phys Rev* 128:2042–2053.
1465 <https://doi.org/10.1103/PhysRev.128.2042>
- 1466 119. LIM K, Grey C (1999) Triple Quantum Cross-Polarization Nmr of ¹H/²⁷Al and ¹⁹F/²³Na Spin Systems in Solid. *Chem*
1467 *Phys Lett* 312:45–56
- 1468 120. Puls SP, Eckert H (2006) Site discrimination in mixed-alkali glasses studied by cross-polarization NMR. *J Phys Chem B*
1469 110:14253–14261. <https://doi.org/10.1021/jp0622511>
- 1470 121. Fu X Bin, Yang G, Wu JZ, et al (2018) Fast Lithium-Ion Transportation in Crystalline Polymer Electrolytes. *ChemPhysChem*
1471 19:45–50. <https://doi.org/10.1002/cphc.201701092>
- 1472 122. Foran GY, Brouwer DH, Goward GR (2017) Quantifying Site-Specific Proton Dynamics in Phosphate Solid Acids by ¹H
1473 Double Quantum NMR Spectroscopy. *J Phys Chem C* 121:.. <https://doi.org/10.1021/acs.jpcc.7b06034>
- 1474 123. Gullion T, Schaefer J (1989) Rotational echo double resonance NMR. *J Magn Reson* 81:196–200.
1475 [https://doi.org/https://doi.org/10.1016/0022-2364\(89\)90280-1](https://doi.org/https://doi.org/10.1016/0022-2364(89)90280-1)
- 1476 124. Eckert H (2010) Short and medium range order in ion-conducting glasses studied by modern solid state NMR techniques.
1477 *Zeitschrift fur Phys Chemie* 224:1591–1653. <https://doi.org/10.1524/zpch.2010.0030>
- 1478 125. Garbow JR, Gullion T (1991) Improvements in REDOR NMR spectroscopy. Minimizing resonance-offset effects. *J Magn*
1479 *Reson* 95:442–445. [https://doi.org/10.1016/0022-2364\(91\)90236-M](https://doi.org/10.1016/0022-2364(91)90236-M)
- 1480 126. Bertmer M, Eckert H (1999) Dephasing of spin echoes by multiple heteronuclear dipolar interactions in rotational echo
1481 double resonance NMR experiments. *Solid State Nucl Magn Reson* 15:139–152.
1482 [https://doi.org/10.1016/S0926-2040\(99\)00050-8](https://doi.org/10.1016/S0926-2040(99)00050-8)
- 1483 127. Chan JCC, Eckert H (2000) Dipolar Coupling Information in Multispin Systems: Application of a Compensated REDOR
1484 NMR Approach to Inorganic Phosphates. *J Magn Reson* 147:170–178. <https://doi.org/10.1006/jmre.2000.2191>
- 1485 128. Voigt N, Van Wüllen L (2012) The mechanism of ionic transport in PAN-based solid polymer electrolytes. *Solid State Ionics*
1486 208:8–16. <https://doi.org/10.1016/j.ssi.2011.11.031>
- 1487 129. Voigt N, Van Wüllen L (2014) The effect of plastic-crystalline succinonitrile on the electrolyte system PEO:LiBF₄: Insights

- 1488 from solid state NMR. *Solid State Ionics* 260:65–75. <https://doi.org/10.1016/j.ssi.2014.03.009>
- 1489 130. Zheng J, Tang M, Hu YY (2016) Lithium Ion Pathway within Li₇La₃Zr₂O₁₂-Polyethylene Oxide Composite Electrolytes.
1490 *Angew Chemie - Int Ed* 55:12538–12542. <https://doi.org/10.1002/anie.201607539>
- 1491 131. Wu N, Chien PH, Li Y, et al (2020) Fast Li⁺ Conduction Mechanism and Interfacial Chemistry of a NASICON/Polymer
1492 Composite Electrolyte. *J Am Chem Soc* 142:2497–2505. <https://doi.org/10.1021/jacs.9b12233>
- 1493 132. Liu M, Cheng Z, Ganapathy S, et al (2019) Tandem Interface and Bulk Li-Ion Transport in a Hybrid Solid Electrolyte with
1494 Microsized Active Filler. *ACS Energy Lett* 4:2336–2342. <https://doi.org/10.1021/acseenergylett.9b01371>
- 1495 133. Xu H, Chien PH, Shi J, et al (2019) High-performance all-solid-state batteries enabled by salt bonding to perovskite in
1496 poly(ethylene oxide). *Proc Natl Acad Sci U S A* 116:18815–18821. <https://doi.org/10.1073/pnas.1907507116>
- 1497 134. Yang T, Zheng J, Cheng Q, et al (2017) Composite Polymer Electrolytes with Li₇La₃Zr₂O₁₂ Garnet-Type Nanowires as
1498 Ceramic Fillers: Mechanism of Conductivity Enhancement and Role of Doping and Morphology. *ACS Appl Mater*
1499 *Interfaces* 9:21773–21780. <https://doi.org/10.1021/acsami.7b03806>
- 1500 135. Yang H, Bright J, Chen B, et al (2020) Chemical interaction and enhanced interfacial ion transport in a ceramic
1501 nanofiber-polymer composite electrolyte for all-solid-state lithium metal batteries. *J Mater Chem A* 8:7261–7272.
1502 <https://doi.org/10.1039/c9ta12495k>
- 1503 136. Martini F, Carignani E, Nardelli F, et al (2020) Glassy and Polymer Dynamics of Elastomers by 1H Field-Cycling NMR
1504 Relaxometry: Effects of Cross-Linking. *Macromolecules* 2:. <https://doi.org/10.1021/acs.macromol.0c01439>
- 1505 137. Jayakody NK, Fraenza CC, Greenbaum SG, et al (2020) NMR Relaxometry and Diffusometry Analysis of Dynamics in Ionic
1506 Liquids and Ionogels for Use in Lithium-Ion Batteries. *J Phys Chem B* 124:6843–6856.
1507 <https://doi.org/10.1021/acs.jpcc.0c02755>
- 1508 138. Rachocki A, Andrzejewska E, Dembna A, Tritt-Goc J (2015) Translational dynamics of ionic liquid imidazolium cations at
1509 solid/liquid interface in gel polymer electrolyte. *Eur Polym J* 71:210–220. <https://doi.org/10.1016/j.eurpolymj.2015.08.001>