



HAL
open science

Nanostructured ZnFe₂O₄: An Exotic Energy Material

Murtaza Bohra, Vidya Alman, Rémi Arras

► **To cite this version:**

Murtaza Bohra, Vidya Alman, Rémi Arras. Nanostructured ZnFe₂O₄: An Exotic Energy Material. Nanomaterials, 2021, 11 (5), pp.1286. 10.3390/nano11051286 . hal-03294668

HAL Id: hal-03294668

<https://hal.science/hal-03294668>

Submitted on 11 Oct 2021

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution 4.0 International License



Review

Nanostructured ZnFe₂O₄: An Exotic Energy Material

Murtaza Bohra ^{1,*}, Vidya Alman ¹ and Rémi Arras ²

¹ Department of Physics, École Centrale School of Engineering (MEC), Mahindra University, Survey Number 62/1A, Bahadurpally Jeedimetla, Hyderabad 500043, India; vidyavasant20pphy010@mahindrauniversity.edu.in

² Centre d'Elaboration de Matériaux et d'Etudes Structurales (CEMES), Université de Toulouse, CNRS, UPS, 29 rue Jeanne Marvig, F-31055 Toulouse, France; remi.arras@cemes.fr

* Correspondence: murtaza.bohra@mahindrauniversity.edu.in

Abstract: More people, more cities; the energy demand increases in consequence and much of that will rely on next-generation smart materials. Zn-ferrites (ZnFe₂O₄) are nonconventional ceramic materials on account of their unique properties, such as chemical and thermal stability and the reduced toxicity of Zn over other metals. Furthermore, the remarkable cation inversion behavior in nanostructured ZnFe₂O₄ extensively cast-off in the high-density magnetic data storage, 5G mobile communication, energy storage devices like Li-ion batteries, supercapacitors, and water splitting for hydrogen production, among others. Here, we review how aforesaid properties can be easily tuned in various ZnFe₂O₄ nanostructures depending on the choice, amount, and oxidation state of metal ions, the specific features of cation arrangement in the crystal lattice and the processing route used for the fabrication.

Keywords: inverted ZnFe₂O₄; nanostructuration; energy harvesting and storage



Citation: Bohra, M.; Alman, V.; Arras, R. Nanostructured ZnFe₂O₄: An Exotic Energy Material. *Nanomaterials* **2021**, *11*, 1286. <https://doi.org/10.3390/nano11051286>

Academic Editors: Oleksandr Tkach and Olena Okhay

Received: 20 April 2021

Accepted: 8 May 2021

Published: 13 May 2021

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2021 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Regardless of the environmental pressure to reduce energy consumption, global power demand is growing—and one of the ways to solve this “looming energy crisis” is through the exploration of novel earth-abundant energy materials [1–4]. Further, the pace of technological change is getting faster, thus the miniaturization of electronic devices is also key [5–7]. These demands can be met by realizing an efficient oxide energy material at the nanoscale by controlling their complex crystal structure with many degrees of freedom (i.e., charge, spin, and orbital) [8]. Oxide materials usually possess high density, display robust physical properties, and show great flexibility to tune their optical, electrical, and magnetic properties, with subtle changes such as elemental substitutions, defect, and strain engineering [1–8]. Among the oxides, earth-abundant Zn-ferrite can be the potential alternative energy material. Zn-ferrites exhibit a unique set of functional properties [9–21]; it possesses a normal spinel structure (ZnFe₂O₄) in the bulk form at room temperature, whereas inverted spinel structure has been observed at the nanoscale. The electronic band structure calculations predict the insulating character of ZnFe₂O₄ [9–12]. The reported room temperature resistivity value of ZnFe₂O₄ is $\rho = 2 \times 10^2$ (Ω -cm), which is two to three orders of magnitude lower than other spinel ferrites [13]. The optical band gap energy [14,15], with values of 2.02 eV and 2.33 eV for the indirect and direct transition near the maxima of UV-Visible absorption curves is suitable for energy harvesting with sufficient amounts of electron-hole pair generation from the solar spectrum, and suitable to drive redox reactions with proper band positions [16]. Appropriate doping of Zn in Fe₃O₄ [17], i.e., a good control of the Zn_yFe_{3-y}O₄ stoichiometry, is one way to tune electric, magnetic, and optical properties which provides a versatile playground to build ZnFe₂O₄ based sensors, solid-state energy conversion devices, and solar cells. The nanostructuration of ZnFe₂O₄ is a second lever of action which enables external tuning competence of the properties by inducing the

cation inversion [18–20]. The cation inversion, an interchange of Zn and Fe atomic positions in the spinel ZnFe_2O_4 strongly depends upon the size of nanostructures produced by different growth methods [19,21]; varying the extent of cation-inversion in spinel structures allows tuning their electronic and spin structure, which eventually can be used to design various spintronic, microwave, and photoelectrochemical (PEC) functionalities. The most important cost factor in energy storage applications is light-absorbing material's efficiency. In the case of ZnFe_2O_4 , the theoretical solar-to-hydrogen (STH) conversion efficiency is estimated to be 17.9% for PEC water splitting [22]. Furthermore, the morphology and size of ZnFe_2O_4 as electrode material are crucial factors in supercapacitors and lithium-ion batteries, wherein theoretical capacity for supercapacitor (2600 F/g) and Li-ion battery (1072 mAhg^{-1}) are higher than when using other ferrites [23,24]. The synergies between Zn and Fe ions in Fe-based binary oxides with large surface area offers higher electrochemical kinetics, active sites, and delivers superior capacitance [25]. Thus, the ability to strongly tune the overall properties of nanostructured ZnFe_2O_4 material demonstrates its pertinence in synergist energy storage applications as well.

Ever since then, ZnFe_2O_4 has been an object of extensive research from both experimental and theoretical points of view, due to its modified and unusual properties that emerge at the nanoscale. In this review, we will emphasize how nanostructured ZnFe_2O_4 oxide can convert, harvest, store, or produce energy. Despite the progress in mastering the nanostructuring of ZnFe_2O_4 , there are open questions that are yet to be fully understood. We will shed light on some of these questions such as ZnFe_2O_4 -property modification at the nanoscale, sensitivity to oxygen stoichiometry, particle size, and surface morphology effects. Finally, we will discuss how ZnFe_2O_4 nanostructures are currently being employed in supercapacitors, lithium-ion batteries, water splitting, low-energy-consumption spintronic, and microwave technologies, which would ultimately offer guidelines for designing futuristic energy-efficient devices.

2. Material Properties of ZnFe_2O_4

2.1. Bulk Crystalline and Spin Structure

Bulk ZnFe_2O_4 possesses a normal cubic spinel XY_2O_4 structure (space group $227-Fd\bar{3}m$; $a = 8.44 \text{ \AA}$) (Figure 1a), wherein oxygen anions occupy 32e Wyckoff sites and form a distorted face-centered cubic (FCC) lattice and large interstices between O^{2-} are partially occupied by iron and zinc cations. One eighth of the tetrahedral positions (labelled A, Wyckoff positions 8a) are occupied by divalent Zn^{2+} cations, while half of the octahedral positions (labelled B, Wyckoff positions 16d) are occupied by trivalent Fe^{3+} cations, leading to the formula $[\text{Zn}^{2+}]_A[\text{Fe}^{3+}_2]_B\text{O}_4$ [26]. One of the distinctive features of the spinels, however, is the wide range of cation distributions accessible in this system and not all spinels have the normal structure as their ground state configuration. There exist several chemistries with the “inverse” spinel configuration where the tetrahedral sites are occupied by the trivalent Y atoms and the octahedral sites are shared equally by both the divalent, X, and trivalent, Y, atoms, i.e., $[\text{Y}]_A[\text{XY}]_B\text{O}_4$ (Figure 1b) [27]. At a finite temperature, mixing of elemental species within the octahedral lattice or across the octahedral and tetrahedral lattices is often observed; it is then possible to define the inversion degree x of the spinel leading associated to the following cation distribution: $[\text{X}_{1-x}\text{Y}_x]_A[\text{X}_x\text{Y}_{2-x}]_B\text{O}_4$. The inversion parameter can vary from 0 (for a normal spinel) to 1 (for an inverse spinel) and adopts a value of 2/3 for a completely random distribution of the metal atoms [28].

Bulk normal spinel ZnFe_2O_4 ideally contains only one type of magnetic ions (Fe^{3+}) and possesses the following magnetic structure (Figure 2). In conventional spinel ferrites, we can mostly consider two superexchange interactions J_{BB} , and J_{AB} between the magnetic ions on the A and B sites and mediated by the oxygen ions. According to the Goodenough–Kanamori–Anderson rules [29,30], the dominant exchange interaction is J_{AB} and corresponds to an antiferromagnetic coupling between atoms in tetrahedral and octahedral sites, because of the nearly 125° angle formed by the oxygen bridge linking these two sites; it turns out to be the ferrimagnetic ordering in many spinel ferrites. However,

as in the normal spinel $ZnFe_2O_4$, the tetrahedral sites are occupied by diamagnetic Zn^{2+} cations ($M(Zn^{2+}) = 0 \mu_B$), such interaction is absent and only a weak antiferromagnetic interaction J_{BB} is operative between Fe^{3+} ions in octahedral sites [19]. This causes the Néel temperature of this oxide to be very low, around 10 K, $ZnFe_2O_4$ being paramagnetic at room temperature.

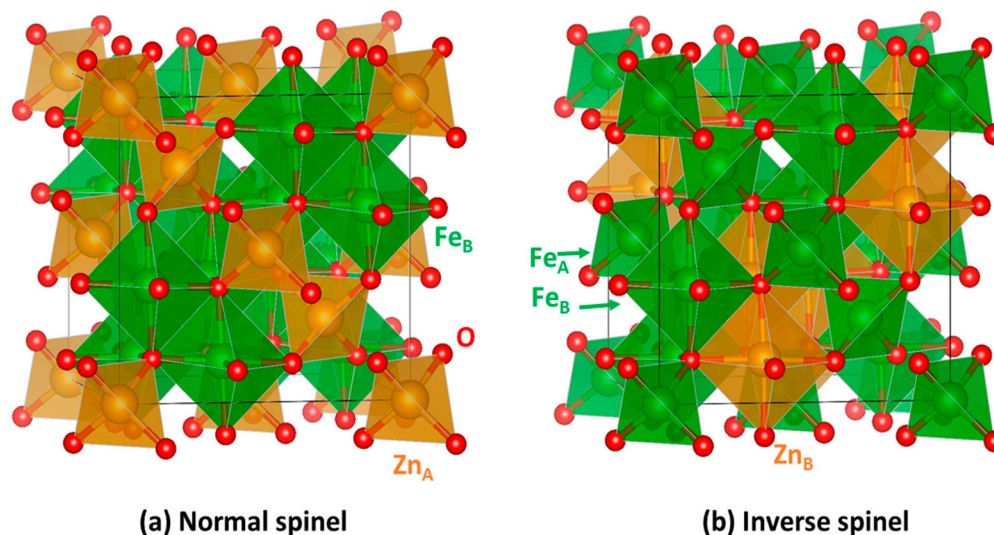


Figure 1. Atomic structure of the spinel zinc ferrite with (a) normal and (b) inverse cation distributions. In each case, the conventional cubic cell (with 8 f.u. of $ZnFe_2O_4$) is delimited by solid black lines. Tetrahedral (A) and Octahedral (B) atomic coordination environments can also be identified by their polyhedra. Orange, green, and red atoms correspond to Zn, Fe and O chemical elements, respectively.

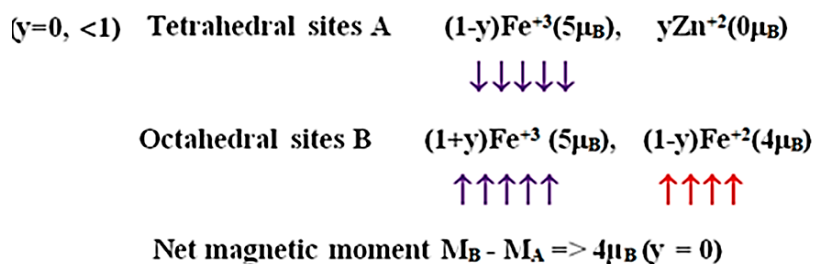
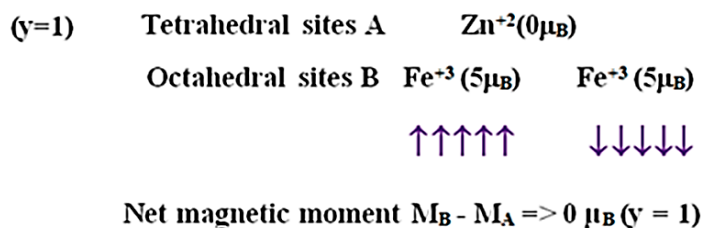


Figure 2. The spin magnetic moment per formula unit of $Zn_yFe_{3-y}O_4$ for $y = 0$ and 1.

A higher Néel temperature can be obtained in the $Zn_yFe_{3-y}O_4$ compound above room temperatures by varying Zn doping concentration (y) in Fe_3O_4 [17], as shown in Figure 3. The spin structures can be given as mixed-valence $[(Zn^{2+})_y(Fe^{3+})_{1-y}]_A[(Fe^{3+})_{1+y}(Fe^{2+})_{1-y}]_B(O^{2-})_4$ inverse spinel, as shown in Figure 2. At low y , the magnetic moments of the A sites are antiparallel to those of the B sites, so the net magnetic moment of the $Zn_yFe_{3-y}O_4$ is $M_S = M_B - M_A = (4 + 6y) \mu_B$. For $y < 0.25$, the M_S of $Zn_yFe_{3-y}O_4$ increases with increasing y , see Figure 3. However, at high Zn contents, the total magnetization is expressed by $M_S = M_B \cos\alpha_{YK} - M_A$, where α_{YK} is the Yafet–Kittel canting angle [17,31,32] between

the magnetic moments in the B sites. For $y > 0.25$, the magnetic moments of remaining Fe^{3+} ions located in the A sites are no longer able to force an antiparallel alignment to all the moments of the iron ions in the B sites. The B sites will then divide themselves into sublattices and the associated magnetic moments will rotate, forming a canting angle between each other, and in consequence of which, a further replacement of the Fe^{3+} ions by the Zn^{2+} ions will lead to a decrease of the magnetic moments in the B sites, that is a decrease of the total M_S .

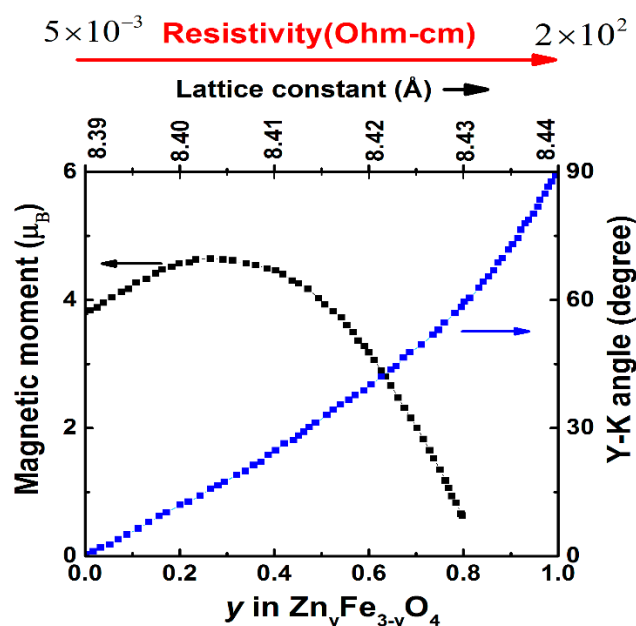



Figure 3. Magnetic moment, Yafet–Kittel angles, and resistivity as a function of y in $\text{Zn}_y\text{Fe}_{3-y}\text{O}_4$ at 300 K (Reproduced with permission from [17]. Copyright American Physical Society, 1976).

We now discuss the relationship between electronic structures and the physical properties of the $\text{Zn}_y\text{Fe}_{3-y}\text{O}_4$ system. With increasing Zn doping, the cubic unit cell expands from 8.39 Å to 8.44 Å, but at the same time induces a decrease of $[\text{Fe}^{2+}]_B/[\text{Fe}^{3+}]_B$ ratio, which in turn reduces the number of itinerant electrons in t_{2g} states at Fermi level, as shown in Figure 4 [33–37]. This causes change in electric resistivity from $5 \times 10^{-3} \Omega \cdot \text{cm}$ of Fe_3O_4 to $2 \times 10^2 \Omega \cdot \text{cm}$ for ZnFe_2O_4 , opening several applications where tunable electric and optical properties are required. However, because of preparation difficulties (particularly in controlling the $\text{Fe}^{2+}/\text{Fe}^{3+}$ ratio), these $\text{Zn}_y\text{Fe}_{3-y}\text{O}_4$ compounds have not been so far commercially exploited.

2.2. Cation Engineering in Nano Regime

Several methods, such as heat treatments, chemical replacements, and the nanostructuring of materials, have been employed to manipulate the distribution of cations between the two interstitial sites of the spinel structures, controlling their physical behaviors [38–40]. Among these methods, stoichiometric ZnFe_2O_4 show striking changes in its crystalline properties by reducing the grain size to the nanometer-sized range [21,40]. When it is prepared at the nanoscale, the energy associated with the low particle size favors a mixed cation distribution in which the Zn^{2+} and Fe^{3+} ions are distributed along the A and B sites giving rise to the inverse spinel structure;





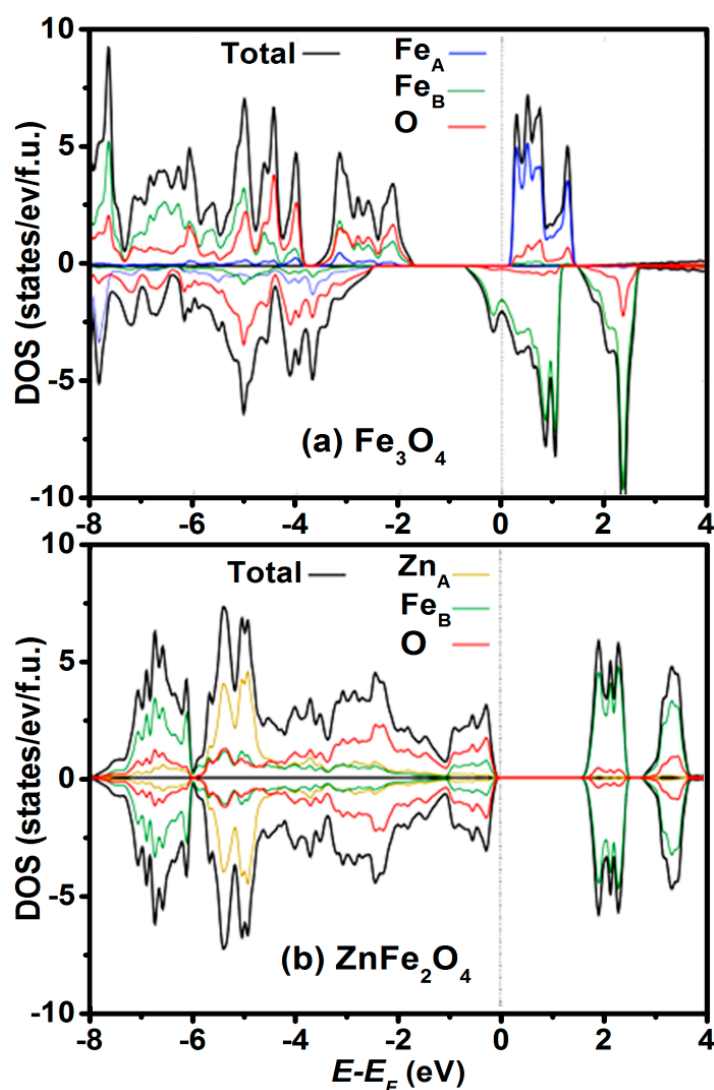


Figure 4. Spin-projected densities of states (DOS) of the $Zn_yFe_{3-y}O_4$ bulk compound obtained from the DFT calculations, using a GGA+ U ($U(Fe,3d) = 4.0$ eV) approximation. (a) $y = 0$ corresponds to the half-metallic and ferrimagnetic magnetite Fe_3O_4 and (b) $y = 1$ to the insulating and antiferromagnetic $ZnFe_2O_4$. Positive and negative DOS represent, respectively, the projection onto majority and minority spin states.

The size of the nanostructures and the resulting cation inversion degree ($x = 0$ to 0.94) vary in different reports, as stoichiometry commonly depends on growth conditions [41]. The inverted $ZnFe_2O_4$ nanostructures have many applications in spintronic and microwave devices and water splitting. These $ZnFe_2O_4$ nanostructures with tunable surface morphology and electrical conductivity are further useful in Li-ion battery and supercapacitors as an electrode [23,24]. Thus, simultaneous measurement of saturation magnetization and conductivity can be used as a tool to approximate cation inversion in the $ZnFe_2O_4$ compound. However, in an oxygen-deficient growth regime, the likely inverted spinel structure is [42,43]



wherein partial reduction of Fe^{3+} into Fe^{2+} is expected at B sites. For a higher oxygen-deficient growth regime, now there is no Zn^{2+} ions are available at B sites and inverted spinel structure is represented a [17]



akin to the Zn doped Fe_3O_4 ($\text{Zn}_y\text{Fe}_{3-y}\text{O}_4$) compound. In extreme condition (high temperature and low oxygen pressure), there is a high chance of dissociation of ZnFe_2O_4 into Fe_3O_4 and ZnO compounds [44]. These transformations greatly affect the magnetic, electric, and optical properties of ZnFe_2O_4 nanostructures.

3. Various ZnFe_2O_4 Nanostructure Morphologies

The physical properties of nanostructured ZnFe_2O_4 can be easily tuned depending on the choice, amount, and oxidation state of metal ions, depending on specific features of cation arrangement in the crystal lattice and finally, depending on the processing route. Recently, a lot of work has been carried out on various nanostructured ZnFe_2O_4 morphologies, including single crystals, epitaxial and polycrystalline thin films, nanoparticles, arrays of colloidal nanocrystals, and heterostructures. The eventual utilization of these morphologies is to develop novel storage devices and this is a critical issue for further investigations.

3.1. Nanoparticles (1 nm < Particle Size < 100 nm)

The recent advances in the synthesis of uniform and size-controllable ZnFe_2O_4 nanocrystals have enabled the size-dependent characterization of their physical properties, as well as their use in applications. The cation inversion in ZnFe_2O_4 nanoparticles varies from method to method. At standard conditions (273 K and 100 kPa), the normal structure is the thermodynamically most stable configuration for bulk ZnFe_2O_4 , however, nanosized ZnFe_2O_4 exhibits a partially inverted spinel structure, which further undergoes structural changes from orthorhombic (30 GPa) to tetragonal (55 GPa) structure at high pressures [28]. Cobos, et al. [40] explored the relationship between microstructure and magnetic properties of ZnFe_2O_4 nanoparticles. The high inversion degree ($x \approx 0.6$) is obtained after 150 h milling with a size of 11 nm in as-milled samples, as shown in Figure 5a, and afterwards, the inversion degree is modified by thermal treatments at different temperatures, i.e., 300, 400, 500, and 600 °C, to finally obtain a very low inversion degree ($x \approx 0.15$), as reported in Figure 5b. It can be noticed that even though the degree of inversion has changed significantly, there is hardly any effect on lattice parameters (8.43–8.44 Å). For $x < 0.25$, antiferromagnetism, ferrimagnetism, and spin frustration can coexist; however, pure ferrimagnetic phase with a maximum magnetization ($M_S = 3.5\mu_B$ per formula unit) can be obtained for $0.25 < x < 0.5$. Finally, for $x > 0.5$, a new antiferromagnetic order appeared due to the overpopulation of nonmagnetic Zn on octahedral sites that leads to equally distributed magnetic cations in octahedral and tetrahedral sites.

A comprehensive work regarding the thermodynamics of the cation disorder and the dependence of the degree of inversion with the temperature has been done by many groups (Figure 5c). The cation distribution in pure ZnFe_2O_4 can be treated as a dynamic equilibrium according to the following interchange reaction, $\text{Zn}_A + \text{Fe}_B \rightleftharpoons \text{Zn}_B + \text{Fe}_A$ between ions being present in A and B sites. Despite we know that the distribution of cations (Fe^{3+} and Zn^{2+}) in an inverse spinel structure governs physical properties, its effect other than magnetic properties of ZnFe_2O_4 are not deliberately explored. Five ZnFe_2O_4 samples with degrees of inversion varying from 0.07 to 0.20 were prepared using a solid-state reaction by Granone, et al. [42] with different annealing temperatures and subsequent quenching. However, their optical band gap energy, with values of 2.02 eV and 2.33 eV for the indirect and direct transition, respectively, is found to be independent of the degree of inversion, as can be seen in the UV-Vis-NIR spectra in Figure 5d. No effect on transition energies due to ligand (O^{2-})-to-metal (Fe^{3+}) charge transfer is observed.

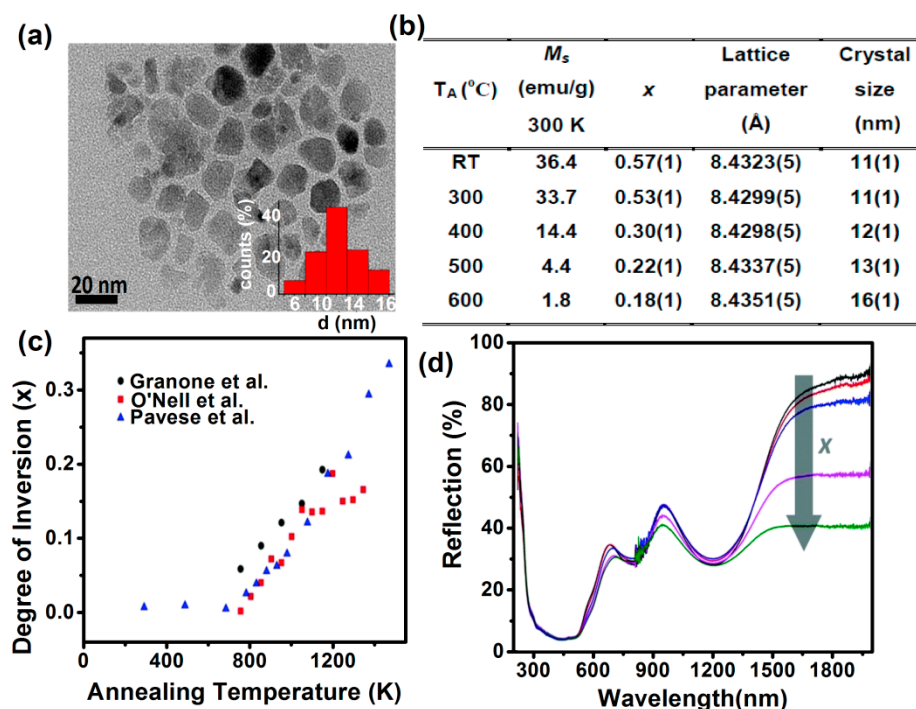


Figure 5. (a) Low-magnification TEM image of $ZnFe_2O_4$ nanoparticles of average size 11 nm. (b) Cation inversion and lattice parameter, M_s and crystal size at different annealing temperatures (Reproduced with permission from [40]. Copyright American Chemical Society, 2019). (c) Degree of inversion, x , versus the annealing temperature comparison of result with values obtained by different groups (Reproduced with permission from [42]. Copyright PCCP Owner Societies, 2018). (d) UV-diffuse reflectance spectrum of $ZnFe_2O_4$ nanoparticles with increasing degree of inversion (— $x = 0.074$; — $x = 0.104$; — $x = 0.134$; — $x = 0.159$; — $x = 0.203$).

It is worth mentioning that annealing of $Zn_yFe_{3-y}O_4$ nanoparticles can also have detrimental effects like the migration of zinc cations, which would lead to the formation of two different crystalline phases, stoichiometric $ZnFe_2O_4$ and hematite [45]. Moreover, $Zn_yFe_{3-y}O_4$ ($0.01 \leq y \leq 0.81$) nanoparticles (3–11 nm) prepared by microwave refluxing method without going through any annealing treatment exhibits physical properties like bulk $Zn_yFe_{3-y}O_4$. Besides, the controlled synthesis of these nanoparticles encounters various obstacles (such as large size distribution, surface segregation, and aggregation), which hinders much potential use in real-world applications.

3.2. Nanocrystalline Thin Films ($1 \text{ nm} < \text{Grain Size} < 100 \text{ nm}$)

Because physical properties strongly depend on the cation distribution in nanocrystalline $ZnFe_2O_4$ thin films, the growth of stoichiometric $ZnFe_2O_4$ thin films by physical vapor deposition (PVD) are crucial. In the literature, nanocrystalline $ZnFe_2O_4$ thin films have been grown by a range of deposition techniques, such as sputtering [19], molecular beam epitaxy (MBE) [46] and pulsed laser deposition (PLD) [39], and chemical methods [32]. In these methods, the low growth temperatures often produce disordered $ZnFe_2O_4$ because it involves quenching of randomly distributed Zn^{+2} and Fe^{+3} vapor phases.

Previously, Bohra et al. [39] deposited $ZnFe_2O_4$ thin films under two different growth conditions: (i) in oxygen partial pressure of 0.16 mbar (ZFPLD1) and (ii) in the vacuum of 1×10^{-5} mbar (ZFPLD2) at in-situ growth temperatures, T_S varies from room temperature (RT) to 850 °C from the $ZnFe_2O_4$ target on amorphous quartz substrate. The nanocrystalline nature of representative ZFPLD1 films with increasing grain sizes 10–70 nm can be seen in Figure 6a. The room temperature magnetic ordering has been observed in low grain-sized ZFPLD1 and ZFPLD2 films as shown in Figure 6b, indicating partial cation inversion. However, this structure goes back to the normal bulk spinel structure in higher grain

sized films, which is paramagnetic. This feature is further confirmed in radio frequency (RF)-sputtered ZnFe_2O_4 films (ZFRF). Interestingly, we can see that even though the same grain-sized ZnFe_2O_4 films synthesized by different growth conditions show different magnetic properties and corresponding cation inversion.

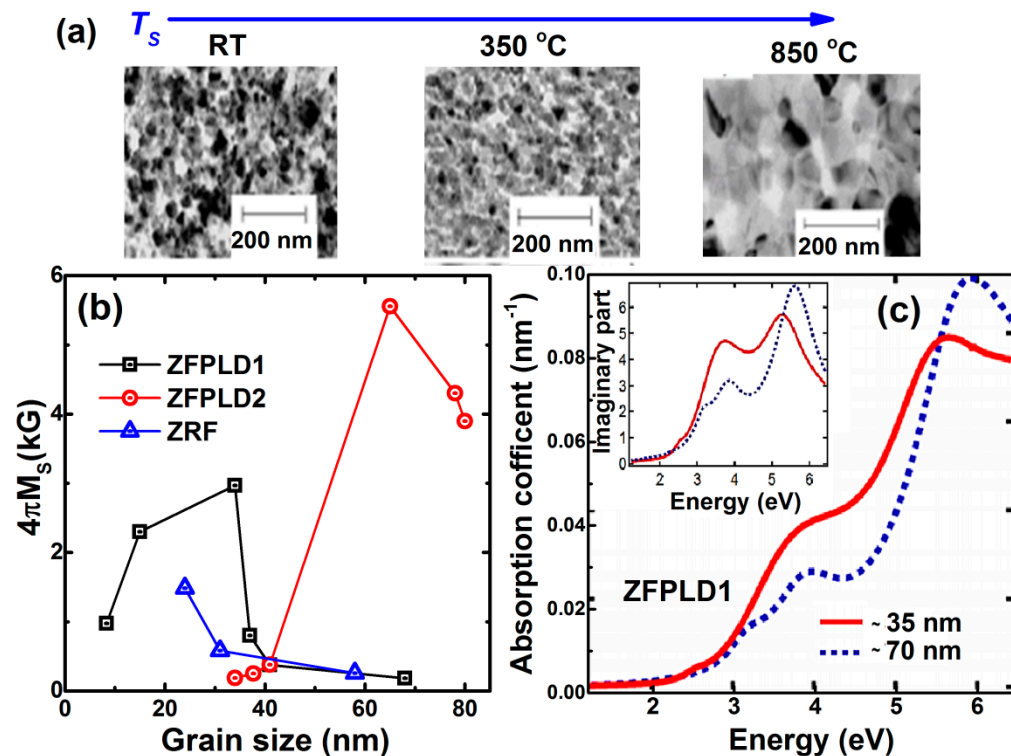


Figure 6. (a) TEM images of ZFPLD1 films grown at T_s of RT, 350 °C and 850 °C exhibit their nanocrystalline nature (b) Room-temperature spontaneous magnetization ($4\pi M_s$) values vs. grain sizes in ZFPLD1, ZFPLD2, and ZFRF films (Reproduced with permission from [39]. Copyright AIP Publishing, 2006). (c) Absorption coefficient of ZFPLD1 films with grain size of ~35 nm (full line) and ~70 nm (dashed line). Corresponding imaginary part of permittivity are plotted in the Inset (Reproduced with permission from [14]. Copyright AIP Publishing, 2015).

Besides, ZFPLD1 films show typical insulator behavior with low oxygen vacancies as can be seen in spectroscopic ellipsometry given in Figure 6c [14], where the absorption edge is situated at the photon energy, $E = 2.5$ eV, hinting presence of only Fe^{+3} ions. The imaginary part of permittivity, $Im\{\epsilon_0\}$ in the Inset, confirms the partial transfer of Fe_{3p} cations from octahedral to tetrahedral sites compared to higher grain-sized films. The peak centered near 3.7 eV becomes enhanced, while the peak centered near 5.6 eV is reduced and shifted to lower E . Likewise, in-situ T_s , an ex-situ annealing temperature (T_A) and film thickness also plays a significant role in controlling cation inversion [47]. The ferrimagnetic ordering develops in nano thick and low T_A annealed ZnFe_2O_4 films [47]. There have been also reports on the growth of nanocrystalline $\text{Zn}_y\text{Fe}_{3-y}\text{O}_4$ films ($y = 0, <1$) with enhanced resistivity values by 10^2 – 10^3 orders, this might be attributed to the presence of large grain boundary volumes [46].

These nanocrystalline ZnFe_2O_4 films create a highly porous morphology which may offer a large number of electrochemically active sites, facilitates Li^+ insertion/extraction inducing the improvement of rate capability and cycling stability [48]. The large surface area and suitable porosity further enhance specific capacitance which allows short diffusion channels for ions to migrate to the interior surface of the electrode and result in an enhanced current response [25].

3.3. Epitaxial Films ($1\text{ nm} < \text{Nano-Thick} < 200\text{ nm}$)

For the efficacious development of ZnFe_2O_4 thin film-based devices, the inherent characteristics of nanocrystalline thin films, such as grain boundary volume, the presence of defects/vacancies, pinholes, and internal stresses can be minimized by growing epitaxial ZnFe_2O_4 thin films. Besides, various technological applications require (i) inverted ferrimagnetic spinel structure [49,50] and (ii) the materials to be semiconducting and preferably transparent [49]. Various groups have attempted to grow epitaxial ZnFe_2O_4 thin films on single-crystal substrates [50,51]. To fabricate semiconducting $\text{Zn}_y\text{Fe}_{3-y}\text{O}_4$ thin films, the depositions are carried out in reducing atmosphere, which causes partial transformation of Fe^{+3} into Fe^{+2} state at octahedral B sites.

Marcu, et al. [44] have investigated, in detail, the room temperature electric transport properties of ZnFe_2O_4 thin films grown by PLD under varying oxygen pressure $P(\text{O}_2)$ and substrate temperature T_S . It can be seen that decreasing both T_S and $P(\text{O}_2)$ result in a decrease in the film resistivity (Figure 7a). The saturated magnetization M_S increases with decreasing both T_S and $P(\text{O}_2)$ (Figure 7b). Apart from the role of Fe^{2+} ion concentration, due to oxygen vacancies, the transport properties are also strongly influenced by structural disorders and vacancies. They also constructed a growth phase diagram about the stability of ZnFe_2O_4 thin films and their possible dissociation into the solid solution of Fe_3O_4 and ZnO at higher T_S and $P(\text{O}_2)$ (Figure 7c). Ferrimagnetic $\text{Zn}_y\text{Fe}_{3-y}\text{O}_4$ ($0 \leq y \leq 0.9$) thin films were grown by Venkateshvaran, et al., both in pure Ar atmosphere and in Ar/ O_2 mixture, using laser MBE [46]. These films exhibit lattice parameters, slightly larger than bulk $\text{Zn}_y\text{Fe}_{3-y}\text{O}_4$ with increasing Zn content (y), as shown in Figure 8a [17]. This feature has been ascribed to the epitaxial strain and larger radius of Zn^{2+} (0.6 \AA) compared to the Fe^{3+} (0.49 \AA). The electrical conductivity (σ) and the saturation magnetization (M_S) show a correlation (Figure 8b) and any spin canting on the B sublattice reduces the M_S , which also results in a reduction of σ , because the hopping amplitude is significantly suppressed if spin magnetic moments of atoms in neighboring B sites are not parallel. This result indicates that epitaxial thin films have less grain boundary volumes, so that itinerant electrons bring ideal and strong double exchange-like interactions between Fe ions at the B site. In particular, the epitaxial $\text{Zn}_y\text{Fe}_{3-y}\text{O}_4$ film is a suitable system to achieve physical properties that are theoretically designed.

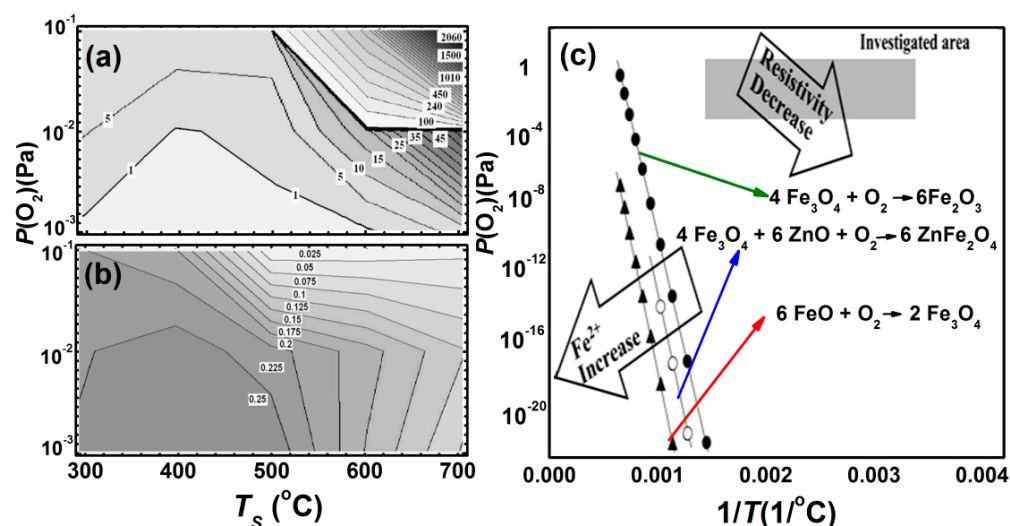


Figure 7. (a) Variation of room temperature resistivity ($\Omega\text{-cm}$) and (b) saturated magnetization (emu/mm^3) of $\text{Zn}_y\text{Fe}_{3-y}\text{O}_4$ thin films with oxygen pressure, $P(\text{O}_2)$ and substrate temperature, T_S , respectively. (c) Comparison between thermodynamic equilibrium lines (the amount of Fe^{2+}) and resistivity variation trend (Reproduced with permission from [44]. Copyright AIP Publishing, 2007).

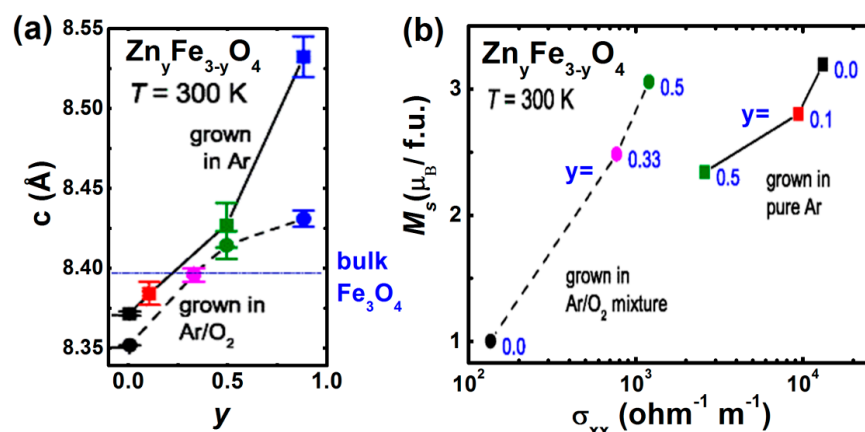


Figure 8. (a) Change in the c -axis lattice parameter of $Zn_yFe_{3-y}O_4$ thin film grown in pure Ar atmosphere (squares) and an Ar/O₂ mixture (circles) with Zn content y . (b) Correlation between saturation magnetization M_s and conductivity σ_{xx} (Reproduced with permission from [46]. Copyright American Physical Society, 2009).

3.4. Other Nanostructured $ZnFe_2O_4$ Geometries

Whilst, quantum amount of work has been done in thin-film form, little is known about the potential use of $ZnFe_2O_4$ for device applications in nanoparticle morphology, as a result, an alternate approach is to tailor the shape of the particles since anisotropy plays a crucial role in deciding many surface-enhanced physical properties. Recently, Saha et al. synthesized [52] nano hollow spheres (NHSs) (shown in Figure 9a) instead of nanoparticles of $Zn_yFe_{3-y}O_4$ by template-free solvothermal method, which shows an increase in M_s values with Zn doping, attaining a maximum at $x = 0.2$ ($M_s = 92.52$ emu/g at 300 K), similarly to the bulk $Zn_yFe_{3-y}O_4$. Therefore, enhanced magnetism with a decrease in conductivity, permittivity, and dipolar interaction enables $Zn_yFe_{3-y}O_4$ NHSs to be a useful material for high-frequency applications [39,53–57].

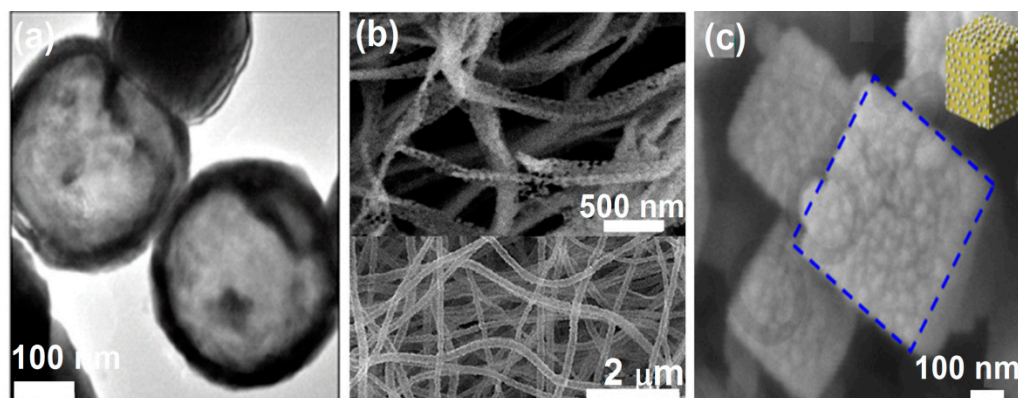


Figure 9. (a) High-resolution TEM of $Zn_{0.3}Fe_{2.7}O_4$ nanospheres (Reproduced with permission from [52]. Copyright American Physical Society, 2019). (b) SEM images of nanotubes in the lower panel and SEM images of nanobelt in the upper panel (Reproduced with permission from [58]. Copyright Elsevier, 2018). (c) SEM images of hollow porous core-shell $ZnFe_2O_4/AgCl$ nanocube (blue dotted line represents cubic facet) coated with EDTA-Ag nanoparticles (Reproduced with permission from [59]. Copyright Elsevier, 2020).

Porous $ZnFe_2O_4$ nanotubes (Figure 9b) have been fabricated by electrospinning followed by two-step calcination in the atmosphere [58]. When the calcination temperature was increased from 600 °C to 650 °C, the $ZnFe_2O_4$ nanotubes evolved into well-crystalline nanobelts (Inset Figure 9b) due to the faster gas diffusion, more active grain growth and atomic diffusion rate caused by the relatively high temperature. The control experiments

indicated the small addition of ZnFe_2O_4 can greatly enhance the photocatalytic activity. The hollow porous core-shell $\text{ZnFe}_2\text{O}_4/\text{AgCl}$ nanocubic coated with EDTA (Ethylenediaminetetraacetic acid)–Ag nanoparticles [59] synthesized via a hydrothermal route followed by a self-etching process can be used as visible-light-triggered antibacterial agent (see Figure 9c). The hollow porous cores not only enhance the reflection and scattering of visible light but also facilitate the transfer rate of photogenerated electrons. These porous nanostructures of ZnFe_2O_4 can display potential practical applications.

4. Applications

These aforementioned tunable behaviors of nanostructured ZnFe_2O_4 have recently been found to have many technological applications in magnetic data storage, microwave components and energy conversion, and storage devices. Besides, they are fundamentally attractive to understand the structure–property correlation.

4.1. Exchange Coupling

4.1.1. Exchange Spring System (Soft + Hard Ferrite)

The composite materials containing hard and soft magnetic materials, which are sufficiently exchange-coupled, can be recognized as an exchange spring magnet [60]. The merging of the high coercive field (H_C) of the hard phase and large saturation magnetization (M_S) of the soft phase can enhance magnetic properties of the permanent magnets [61]. Soft-magnetic inverted ZnFe_2O_4 nanostructure has several merits, such as high chemical stability and corrosion resistivity, superior magnetic properties, and low cost [61,62]. Thus, combining soft phase ZnFe_2O_4 along with hard phase $\text{SrFe}_{12}\text{O}_{19}$ has stimulated the researcher's interest recently in high-performance nanocomposite magnets. Figure 10a shows room temperature exchange coupling property in $\text{SrFe}_{12}\text{O}_{19}/\text{ZnFe}_2\text{O}_4$ composites synthesized by coprecipitation method [61] with larger M_S and H_C values as compared to the pure $\text{SrFe}_{12}\text{O}_{19}$. The molar ratio of $\text{SrFe}_{12}\text{O}_{19}$ influences the magnetic properties of $\text{SrFe}_{12}\text{O}_{19}/\text{ZnFe}_2\text{O}_4$ composites (Figure 10b). On the other hand, using normal spinel ZnFe_2O_4 in these composites [62] yields M_S , and H_C of 35 emu/g and 2254 G (Figure 10c), respectively, indicating the composite has a greater capacity to avoid demagnetization. Nanocrystalline $\text{CoFe}_2\text{O}_4/\text{ZnFe}_2\text{O}_4$ bilayers (Figure 10d) also exhibit significant exchange coupling at low temperatures 10 K, which also retains up to room temperature for specific growth conditions [60].

4.1.2. Exchange Bias (AFM/FM Interfaces)

The exchange bias (EB) is the magnetic interface effect that couples an antiferromagnetic (AFM) and a ferromagnetic (FM) system [63]. It manifests itself as a shift H_{EB} of the M – H loop along the magnetic field (H) axis and as an enhancement of the coercive field, H_C , when the system is cooled down in an external magnetic field through the magnetic ordering temperatures of the AFM (T_N) and FM (T_C) phases. Exchange bias is one of the key concepts in spin valves, which has revolutionized the field of magnetic recording and memory devices, by allowing the pinning of the magnetization direction of one of the magnetic electrodes. Lin, et al. [64] fabricated an all-oxide spin valve with the ferroelectric antiferromagnet BiFeO_3 (BFO) as the pinning AFM-layer ($T_N = 385^\circ\text{C}$). The multi-layered spin-valve, where two ferrimagnetic (FM) $\text{Zn}_{0.7}\text{Ni}_{0.3}\text{Fe}_2\text{O}_4$ (ZNFO) layers are separated by a nonmagnetic conducting layer, was grown epitaxially on a (001) SrTiO_3 substrate, as shown in Figure 11a. They discussed some of the key physical and material issues for building up such novel devices in particular the hetero-epitaxy-induced strain effects on the electrical and magnetic properties of each layer and the establishment of exchange bias between BFO and ZNFO. The spin-valve was field annealed from a temperature above the high Néel point of BFO, after which a very large exchange bias field (H_{ex}) was achieved at 5 K (Figure 11b) and kept at a decent value at room temperature (Figure 11c). The magnetoresistance (MR) achieved at room temperature (Figure 11d) was magnetically tunable in a similar way to conventional metallic spin valves.

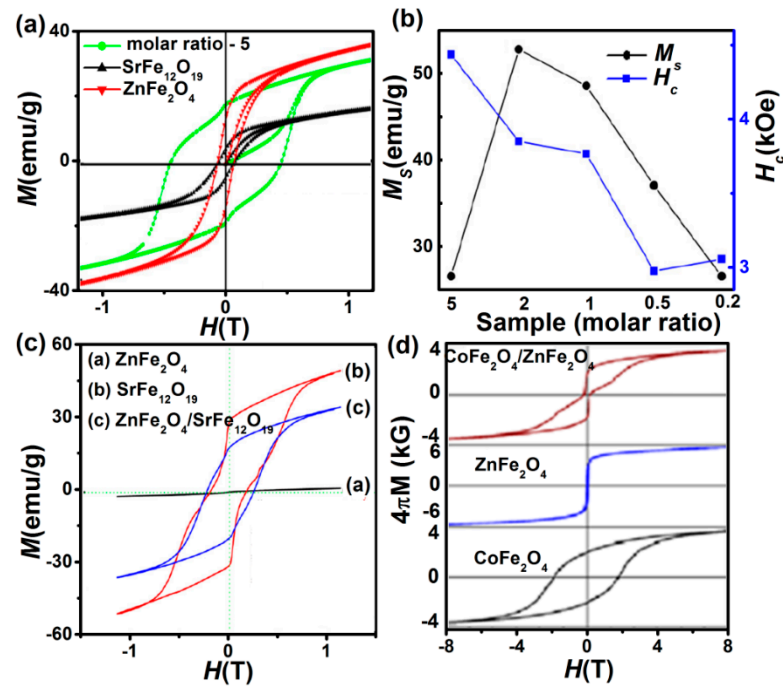


Figure 10. (a) M - H loops of SrFe₁₂O₁₉/ZnFe₂O₄ with molar ratio 5 (Reproduced with permission from [61]. Copyright Elsevier, 2018). (b) Variation of M_s and H_c values with molar ratio changing from 5 to 0.2. (c) M - H loops of SrFe₁₂O₁₉/ZnFe₂O₄ with normal structured ZnFe₂O₄ (Reproduced with permission from [62]. Copyright Elsevier, 2013). (d) M - H loops of exchange-coupled CoFe₂O₄/ZnFe₂O₄ bilayer at 10 K (Reproduced with permission from [60]. Copyright AIP Publishing, 2013).

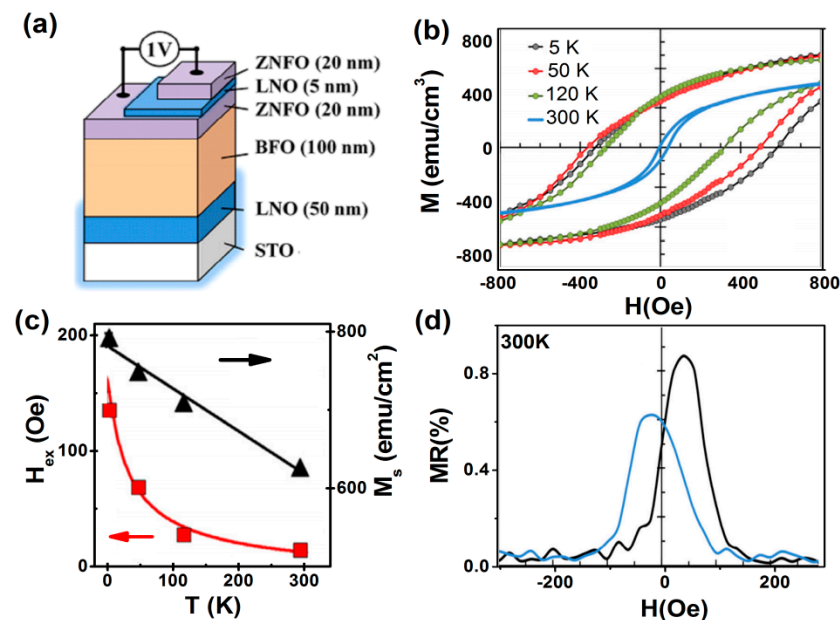


Figure 11. (a) Schematic of spin valve with the ferroelectric anti-ferromagnet BFO as the pinning layer and the proposed materials for other epitaxial layers. (b) M - H loops recorded upon heating up. The sample was annealed at $H_{\text{ann}} = 3$ kOe from 400 °C to room temperature before the measurements. The arrow indicates the direction of H_{ann} . (c) Temperature dependence of the exchange bias (H_{ex}) and saturation magnetization (M_s). (d) The MR measured in such a spin valve heterostructures (Reproduced with permission from [64]. Copyright Elsevier, 2013).

4.2. High-Frequency Applications

Performance of on-chip X-band (8–12 GHz) inductor, integrated with magnetic film can enhance its inductance density as well as the quality factor, facilitating miniaturization of RF devices and reducing dependency on silicon [54–56]. To find a suitable candidate material, whose ferromagnetic resonance frequency (f_{FMR}) is above 6 GHz, i.e., in the expected new spectrum for 5G mobile communication, is now indispensable. Among metallic alloys, amorphous films, granular films and soft-magnetic ferrites, the first three exhibits very high permeability that results in >20% enhancement of inductance, but their applicability is limited to a few GHz; eddy-current losses and ferromagnetic resonance losses become prohibitively large at higher frequencies [55]. However, the family of ferrites with very high electrical resistivity and high f_{FMR} values can limit the aforesaid losses up to a few tens of GHz.

A crucial challenge is the growth of thick ferrite films on a silicon chip in a CMOS (complementary metal oxide semiconductor)-compatible manner [55]. Most PVD methods are either non-scalable or require high processing temperatures (in-situ or ex-situ annealing ≥ 500 °C). On the other hand, the low-temperature chemical methods require strict control of the pH of the solution, which may otherwise corrode the on-chip metal wiring. Recently, Sai et al. deposited partially inverted ZnFe_2O_4 film with soft magnetic characteristics ($M_S = 130$ emu/cc and $H_C = 120$ Oe) directly on a Si-CMOS integrated circuit by Microwave-Assisted Synthesis Technique (MAST) at 200 °C [54,55]. These films showed FMR frequency above 30 GHz, with negligible FMR loss below 15 GHz, therefore, they could be used as inductor core in the frequency range up to 15 GHz and as an electromagnetic noise suppressor around 30 GHz. Up to 13% enhancement in inductance density and 25% enhancement in the quality factor were demonstrated at 10 GHz, giving the highest-density (450 nH/mm²) on-chip ferrite-core inductor. To harness the best effect of magnetic film, a complete magnetic path, i.e., complete encapsulation of the coil, is necessary. By utilizing the ability of MAST to deposit ZnFe_2O_4 film conformally, three sides of the on-chip coil are covered by ZnFe_2O_4 film in a single step. The resulting coil structure is demonstrated both schematically and with SEM images in Figure 12a–d. An enhancement of the Q-factor by 78% is achieved, as shown in Figure 12e. It is to be noted that the magnetic path is, nevertheless, not closed. A very large increase in inductance and inductance density can be achieved if the coil can be fabricated on a ferrite layer instead of the interlayer dielectric. An important aspect of the development of RF-CMOS integrated circuits is the design and fabrication of the magnetic-core inductor at low temperature and scalable level, for this purpose, RF sputtered inverted ZnFe_2O_4 films of narrow FMR line width of 40 Oe (at 9 GHz) [53] could then be explored to meet the ever-increasing demand for functionality.

4.3. Lithium-Ion Batteries

Global Lithium-ion battery (LIBs) deployments stand poised to grow substantially for electric vehicles and renewable energy storage in the coming years, but it will be necessary to search/design novel electrode materials. There have been many reports on the ZnFe_2O_4 as anode materials for LIBs owing to their high electrochemical properties (high specific capacity, cycling performance, rate capability, and reversible specific capacity). Instead, traditional graphite anodes exhibit theoretical specific capacity only 372 mAhg⁻¹ [65,66], limited energy density, and poor electrochemical performance, unsatisfying the demand of many practical applications. The Li-ion storage mechanism of ZnFe_2O_4 involves conversion and alloying reaction, where each unit of ZnFe_2O_4 has been reported to be able to store up to 9 units of Li⁺ ions, thus giving it a high theoretical capacity of 1072 mAhg⁻¹ [24]. Compared to other spinel transition-metal oxides, ZnFe_2O_4 possess the advantage to be non-toxic and less expensive than MCo_2O_4 compounds, while Mn-based spinel oxides display lower electrical conductivity. Magnetite, Fe_3O_4 , has a theoretical capacity of 900 mAhg⁻¹, but it displays a high working potential of 2.1 V vs. Li⁺/Li, limiting thus the energy storage capability [67,68]. It has been evidenced that Zn-doping of Fe_3O_4 , with

carbon coating, can enhance the electrochemical performance by increasing the electronic and ionic conductivity and could work for relatively low voltage [69].







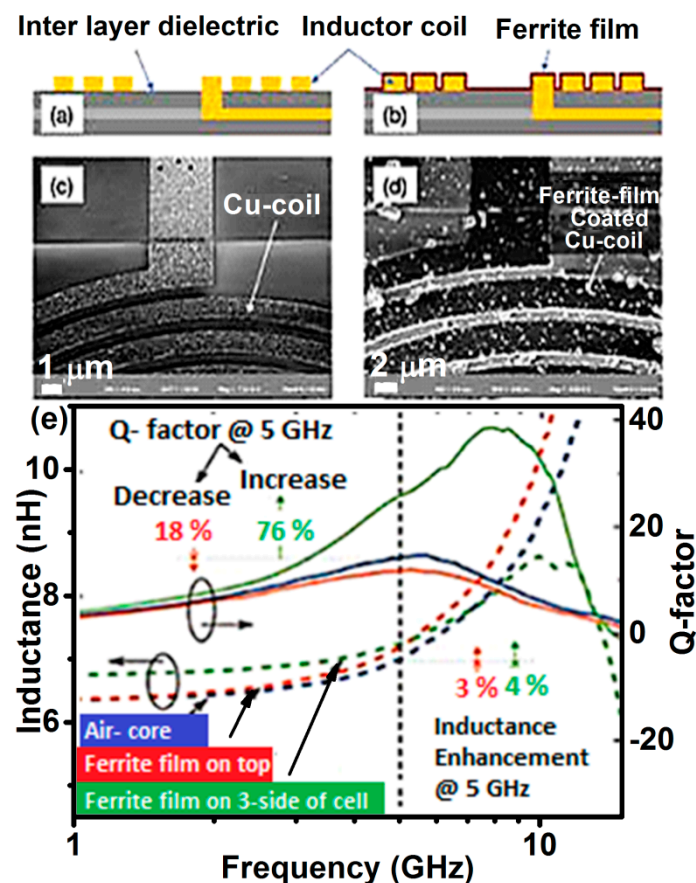


Figure 12. Schematic of inductor coil on a Si-CMOS chip (a) with passivation removed from 3-sides of the coil, and (b) with ZnFe_2O_4 thin (250 nm) film-coated conformally; (c,d) show the SEM images of the coil before and after ferrite coating; (e) Measured inductance and Q-factor of the on-chip inductance with ferrite film deposited only on top (in red) and surrounding 3-sides of the coil (in green) (Reproduced with permission from [55]. Electrochemical Society, 2017).

Prior studies have shown that reducing particle size can help to relax the strain, and have a high surface-to-volume ratio and reduced transport length, which can lead to increased cyclability. Based on the Li storage mechanism [24,70,71] of ZnFe_2O_4 , the first discharge cycle is described as follows:



In recharging process, the ferrite molecule cannot be recovered and the reactions involve the newly formed oxides ZnO and Fe_2O_3 [24,72,73]:



It is interesting to note that the formation of the LiZn alloy has recently been debated as experimental measurements associated with DFT calculations have found no evidence

of it and suggested the formation of FeO instead of Fe₂O₃ (Figure 13) [74,75]. This study also shed light on the structure of Li_xZnFe₂O₄, in which Li atoms are first inserted in the vacant 16c Wyckoff sites (for 0 < x ≤ 1). When increasing the Li content (x > 0.25), some migration of Zn²⁺ cations from tetrahedral 8a sites to vacant 16c octahedral sites also occur; when no vacant 16 sites are left, remaining Li atoms will take place in 8a sites (1 < x ≤ 2).

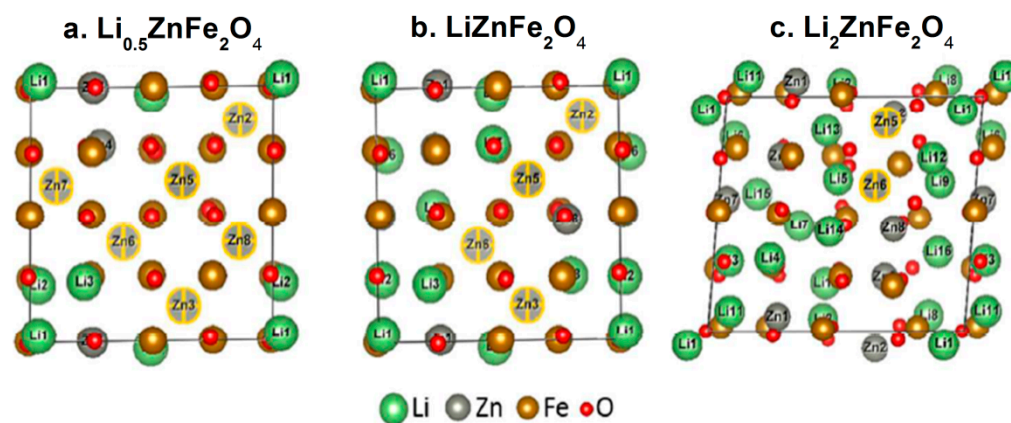


Figure 13. Structures of (a) Li_{0.5}ZnFe₂O₄, (b) LiZnFe₂O₄, and (c) Li₂ZnFe₂O₄. (grey with a yellow circle: Zn²⁺ ions in 8a site) (Reproduced with permission from [74]. Copyright American Chemical Society, 2017).

The porous structures have attracted significant attention, due to their high surface area and buffer effects, which are preferable for improving the electrochemical properties [76]. However porous framework can not only accommodate the volume expansion/contraction when reacting with Li⁺, but also provide more reaction sites on the surface and shorten the diffusion distance of Li⁺ and electrons. Hou, et al. reported the porous ZnFe₂O₄ inflorescence spicate structure assembled by spherical nanoparticles as primary building particles (Figure 14a), which is synthesized by the precipitation method and subsequent thermal treatment by using cetyltrimethylammonium bromide (CTAB) as a surfactant [77]. The reversible capacity for spicate ZnFe₂O₄ remains 1398 mAhg⁻¹ over 100 cycles, which is higher than that of reported different morphologies of pure ZnFe₂O₄ electrodes (Table 1). The cyclic performances and Coulombic efficiencies for ZnFe₂O₄ at a high current density 100 mA g⁻¹ are illustrated in Figure 14b. The discharge capacity of the ZnFe₂O₄ electrode is much higher than its theoretical capacity, which is due to the high active surface and interface area of the porous nanostructures.

Table 1. Morphology dependent electrochemical performance of ZnFe₂O₄ as electrode.

Morphology	Reversible Capacity mAh g ⁻¹	Cycle	Current Rate mA g ⁻¹	Ref.
Thin film	434	100	10	[78]
Nanoparticles	841	50	60	[79]
Nanofibers	733	30	60	[80]
Nano-octahedrons	910	80	60	[81]
Nanorod	900	50	100	[82]
Cubic nanoparticles	367	50	60	[83]
Hollow spheres	900	50	65	[70]
Hollow microspheres	1200	120	100	[84]
Hollow nanospheres	1101	120	200	[85]

Moreover, the ZnFe₂O₄ composite displays electrochemical properties. For instance, the conducting polymer poly(3,4-ethylene dioxythiophene) (PEDOT) coated ZnFe₂O₄ composites (Figure 14c) delivered a discharge capacity of 1510.5 mAhg⁻¹ at 100 mA g⁻¹ after 200 cycles, exhibiting the high performance over others and were much larger than

that of pure ZnFe_2O_4 . The high-rate cycling performance and corresponding Coulombic efficiencies of the ZFPE-15 electrode were tested at a large current density of 1 A g^{-1} , as shown in Figure 14d. The electrically conductive PEDOT coating facilitates electron transfer from ZnFe_2O_4 and acts as a buffer matrix to restrain volume expansion, showing that ZnFe_2O_4 -15 wt% PEDOT composites (ZFPE-15) are promising anode materials for use in LIBs [86]. Hence developments in LIBs provide new insights about the processes ruling their fundamental chemical properties and this should inspire more efforts in developing low-cost ZnFe_2O_4 based electrodes for LIBs, with enhanced rate capability and cycling life.


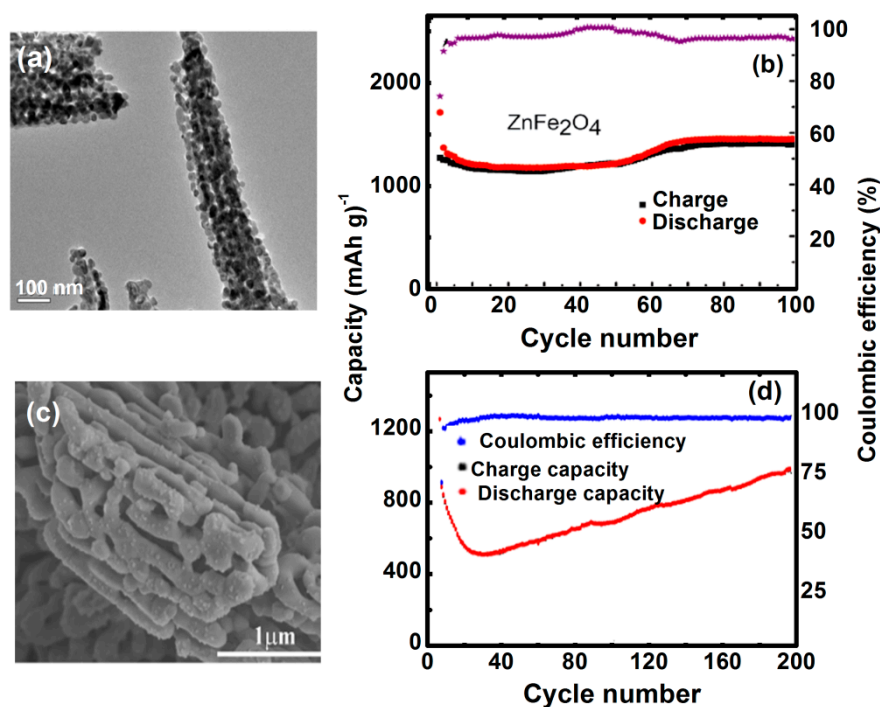


Figure 14. (a) TEM image of ZnFe_2O_4 . (b) Cycle performances and Coulombic efficiencies (CE) of ZnFe_2O_4 at a current density of 100 mA g^{-1} (Reproduced with permission from [77]. Copyright Royal Society of Chemistry, 2015). and (c) SEM image of ZFPE-15 and (d) cycle performances and Coulombic efficiencies (CE) at a current density of 1 A g^{-1} (Reproduced with permission from [86]. Copyright Elsevier, 2020).

4.4. Photoelectrochemical (PEC) Water Splitting

Among the various paths for solar fuel production, the photochemical dissociation of water into its constituent parts, H_2 and O_2 offer the simplest and potentially efficient approach which requires virtually zero energy input except sunlight to produce clean and storable hydrogen as a fuel. Many photocatalytic anode materials suffer from poor light absorption at visible wavelengths, poor charge transport, and/or poor photo-stability in aqueous electrolyte solutions. A theoretical solar-to-hydrogen (STH) conversion efficiency close to 20% was predicted for the n-type narrow bandgap ($E_g = 1.9 \text{ eV}$) ZnFe_2O_4 semiconductor. A sufficient positive valence band of ZnFe_2O_4 can drive PEC water-splitting when used as an anode material [16,87].

The electrochemical cell under basic conditions (see Figure 15a) can undergo redox reaction, like hydrogen evolution reaction (HER) and oxygen evolution reaction (OER), which can be expressed as:



However, different treatments on the ZnFe_2O_4 electrode shows enhancement in water splitting photocurrent density (J) such as, post-synthesis with hydrogenation (at mild temperature) enhances electrical conductivity by introducing oxygen vacancies [88]. Hybrid microwave annealing treatment is better than conventional annealing treatment [89,90], and doping of semiconductor (e.g., p-type Co- ZnFe_2O_4) [91] leads to change in electrical conductivity and offers high crystallinity.

Guo, et al. [92] synthesized Ti^{4+} doped ZnFe_2O_4 as anode material by effective spray pyrolysis method for water splitting application. The substitution of Fe^{3+} by Ti^{4+} enhances the charge carrier concentration and electron transfer efficiency. Ti-doped ZnFe_2O_4 photoanodes exhibit, $J = 0.35 \text{ mA cm}^{-2}$ at 1.23 V vs. RHE (reversible hydrogen electrode), which is 8.75 times higher than that of the pure ZnFe_2O_4 photoanodes, as shown in Figure 15b [92]. 1-D ZnFe_2O_4 nanorods with Al_2O_3 passivation layer at different annealing temperatures showed an increased J value of 0.48 mA/cm^2 at 1.23 V vs. RHE (Figure 15c,d) compared to seven times and three times higher than pure ZnFe_2O_4 annealed at 550°C and 800°C , respectively. High-temperature annealing and coating of an Al_2O_3 layer helped to minimize surface defects and reduced surface recombination due to the chemical passivation effect [93]. On the other hand, PEC performance of inverted ZnFe_2O_4 nanorod photoanode prepared by conversion route [94], shown in Figure 15e [95] strongly depends upon cation inversion (x), which further depends upon growth temperatures. The J - V curves in Figure 15f for 600°C grown sample (ZFO-600, $x = 0.18$) delivers the highest J surpassing 0.8 mA cm^{-2} at 1.23 V and rising to 1.7 mA cm^{-2} at 1.6 V versus RHE. While ZFO-800, $x = 0.13$ sample exhibited the most favorable photocurrent onset potential (at $\approx 0.8 \text{ V}$ vs. RHE), J remained below 1.0 mA cm^{-2} . By contrast, the ZFO-500, $x = 0.3$ sample exhibited a more positive onset potential ($\approx 1.2 \text{ V}$ vs. RHE) but J was higher than ZFO-800 at the high applied potential. The NiFe_2O_4 (NFO) coated ZnFe_2O_4 nanorods show higher performance as photoanodes. The higher x is related to the superior charge transport and changes in x result in changes in the electronic structure. However, still, J is far below the theoretical maximum value of $\approx 11 \text{ mA cm}^{-2}$ with ZFO which has to increase by overcoming fundamental limitations, such as poor absorption coefficient and bulk charge separation, for enhancement of PEC water splitting performance.

4.5. Electrochemical Supercapacitors

Electrochemical supercapacitors are energy storage devices with properties intermediate to those of batteries and electrostatic capacitors. They exhibit high power density (ten times higher than batteries), high cycling stability, high energy capacity, storage for a shorter period, and high charging/discharging, which makes them a contender for next-generation power devices [4]. ZnFe_2O_4 is a suitable material for electrochemical applications, due to its eco-friendly nature, sufficient resources, cost-effectiveness, strong redox process, and an extraordinary theoretical capacity of 2600 F g^{-1} [23,96]. However, its lower conductivity and low cycling stability make it unsuitable for efficient supercapacitors. To overcome these issues, conducting materials were added to the ZnFe_2O_4 to enhance the electronic conductivity and cycling stability [97]. Javed, et al. fabricated flexible supercapacitors with ZnFe_2O_4 nanowall (NWs) arrays deposited on carbon textile (ZFO-NWs-CT) electrode by hydrothermal method, as shown in Figure 16a. These supercapacitors exhibit capacitance of 620 F g^{-1} at 5 mVs^{-1} compared to the pure ZnFe_2O_4 NWs (Figure 16b) with a long life of 10,000 cycles. The Ragone plot in Figure 16c of ZFO-NWs-CT supercapacitors shows a high energy density of 85 Wh kg^{-1} at a power density of 1000 W kg^{-1} [98].

Vadiyar, et al. [99] synthesized composite of ZnFe_2O_4 nano-flakes and carbon nanoparticles are shown in Figure 16d by in-situ bio-mediated green rotational chemical bath deposition, which demonstrates specific capacitance of 1884 F g^{-1} at a current density of 5 mA cm^{-2} (Figure 16e) and energy density of 81 Wh kg^{-1} at a power density of 3.9 kW kg^{-1} , as shown in Figure 16f. This supercapacitor also exhibits long cycle stability of 35,000 cycles by losing only 2% capacitance, which is attributed to the self-assembled organization of the heterostructures with the addition of carbon to ZnFe_2O_4 [99]. Recently,

a nanocomposite of ZnFe_2O_4 nanorods and reduced graphene oxide showed higher specific capacitance 1419 F/g with cyclic stability of 93% after 5000 cycles at the scan rate of 10 mV/s. Thus, ZnFe_2O_4 /carbon hybrid materials are promising electrode material for supercapacitor.

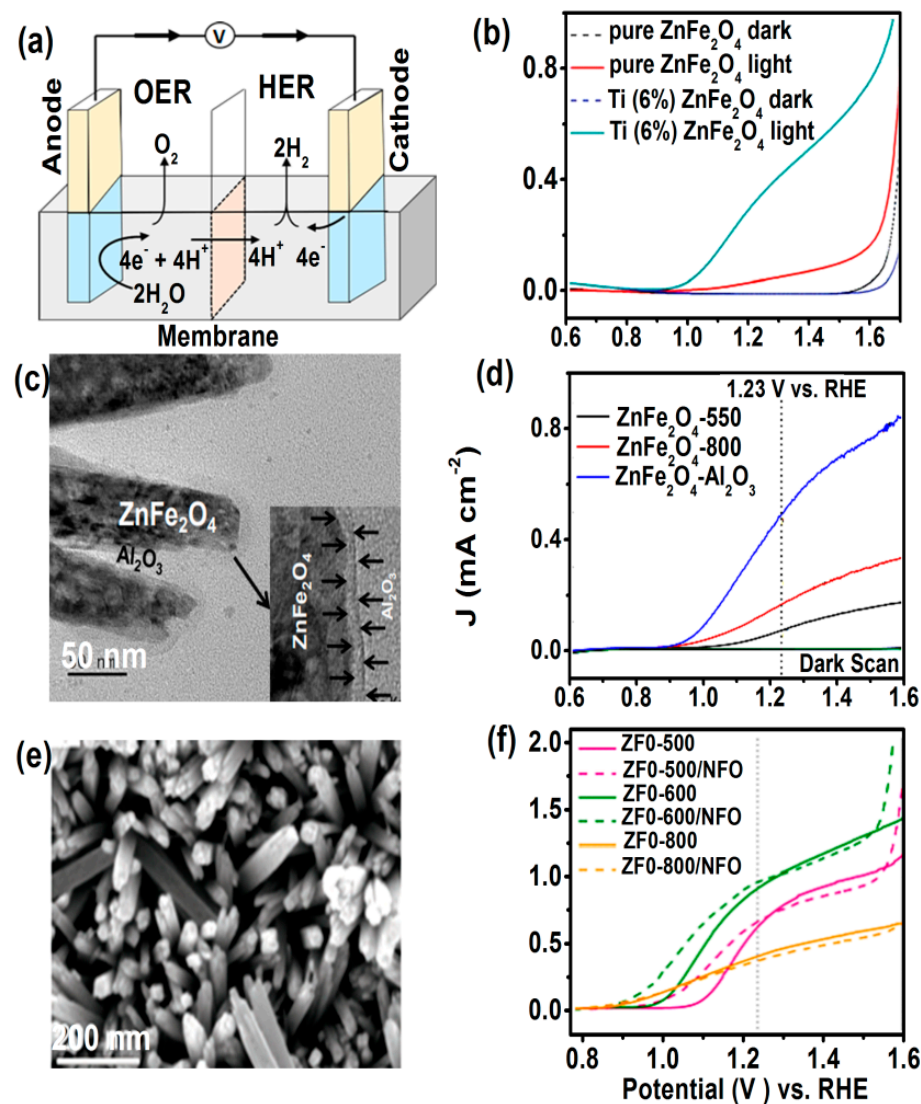


Figure 15. (a) Schematic of electrolysis cell for water splitting, (b) current density J vs. potential curves, V of ZnFe_2O_4 photoanodes (Reproduced with permission from [92]. Copyright Royal Society of Chemistry, 2017). (c,d) TEM image of $\text{ZnFe}_2\text{O}_4\text{-Al}_2\text{O}_3$ and corresponding J vs. V curves (Reproduced with permission from [93]. Copyright Royal Society of Chemistry, 2018). (e) SEM images ZnFe_2O_4 nanorod, ZFO-500 (f) J vs. V curves (Reproduced with permission from [95]. Copyright Wiley, 2018).

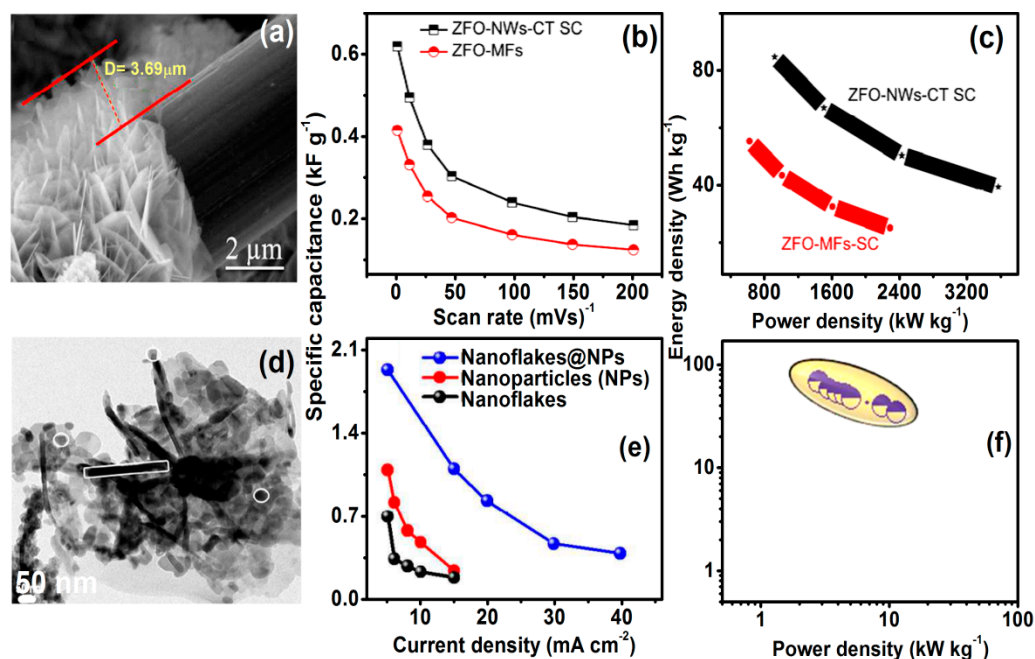


Figure 16. Hydrothermal method: (a) SEM images of ZFO precursor nanowall arrays on CT fibres, (b) specific capacitances as a function of scan rate, and (c) comparative Ragone plots (Reproduced with permission from [98]. Copyright Elsevier, 2019). In-situ bio-mediated green rotational chemical bath deposition: (d) TEM of ZnFe_2O_4 nano-flakes@ $\text{ZnFe}_2\text{O}_4/\text{C}$ nanoparticle thin film heterostructure, (e) plot of specific capacitance (F g^{-1}) vs. current density (mA cm^{-2}) and (f) Ragone plot (Reproduced with permission from [99]. Copyright American Chemical Society, 2017).

5. Conclusions

Current day research aims at revolutionizing energy storage devices with advanced materials that can operate at low power consumption with high speed, yet without compromising the aim of shrinking their size. The search of more efficient materials should not be done at the expense of the environment or health preservation. For this goal, materials such as ZnFe_2O_4 possess many advantages, owing to its physico-chemical properties, rich phase diagram with multiple conductive or magnetic states which are dictated by its complex and open atomic structure. The presented comprehensive review on the growth methodologies of various ZnFe_2O_4 nanostructures, (nanoparticles and epi/poly thin films *etc.*) and its famed cation inversion engineering not only portrays the current knowledge about possible changes brought forth in structural/chemical, electronic, and magnetic properties, but also helps to envision the future research directions to develop ZnFe_2O_4 towards efficient energy material.

Moreover, its spinel structure being relatively “open”, many vacant crystallographic sites can facilitate the intercalation of (mobile) dopants, which in turn can enlarge the number of applications of such material. Further, as summarized in this review, different growth conditions can be used to control and tune the magnitude of defects and grain boundaries, off stoichiometry, non-zero $\text{Fe}^{2+}/\text{Fe}^{3+}$ ratios, and micro/nano strains, which ultimately allows designing the overall properties to enhance the energy-efficiency of ZnFe_2O_4 material. Considering nanoscale cation engineering and with the achievable control over growth strategies of various ZnFe_2O_4 nanostructures, ZnFe_2O_4 can be a potential material in the following futuristic applications:

- Different spintronics devices, possibly with low-energy operation cost, can be constructed by using an inverted stoichiometric ZnFe_2O_4 thin film as ferrimagnetic layer in magnetic tunnel junctions, as a barrier layer in spin filtering devices, oxygen-deficient $\text{Zn}_y\text{Fe}_{3-y}\text{O}_{4-\delta}$ thin film as a conducting layer could be used in homo-epitaxial devices, provided with a fine control of the stoichiometry during the growth.

- Inverted ZnFe₂O₄ thin layer with low microwave loss can be a potential material for high-frequency applications, such as 5G mobile communication.
- Inverted ZnFe₂O₄ nanostructures are emerging photoanode material for photoelectrochemical solar fuel productions. Cation disorder in ZnFe₂O₄ facilitates photogenerated charge separation and increased charge carrier transport.
- ZnFe₂O₄ used as an electrode in a Li-ion battery demonstrated large charge/discharge capacity and cycle stability. Highly porous surface and wide voids in ZnFe₂O₄ nanostructures play a critical role in enhancing electrochemical reactions. The suitable cathode and stable electrolyte materials are the prerequisite to form ZnFe₂O₄-based Li-ion battery considering high working voltage of electrode.
- Various ZnFe₂O₄-based heterostructures and nanocomposites with high conducting property can boost cycle stability and energy density for high-performance supercapacitors.

Convincingly, the cation inversion and various porous nanostructures are important factors to tailor the properties of ZnFe₂O₄ which can potentially lead into useful nanoscale devices, although scalable energy-efficient devices using ZnFe₂O₄ at nanoscale remains to be major challenge to date, and may require significant advancements in research and development efforts combined with fundamental research on ZnFe₂O₄.

Author Contributions: Conceptualization, M.B.; writing—original draft preparation, M.B., R.A. and V.A.; writing—review and editing, M.B., R.A. and V.A.; supervision, M.B.; project administration, M.B.; funding acquisition, M.B. All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by International Bilateral Cooperation Division of DST, India for a grant under INT/BLG/P-14/2019 (India-Bulgaria Joint Research Projects scheme). The authors also acknowledge the Ministry of Science and Technology (MOST), Taiwan for financial support under Grants Nor. MOST-109-2112-M-110-012.

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: No new data were created or analyzed in this study. Data sharing is not applicable to this article.

Acknowledgments: Authors grateful to acknowledge the valuable discussion with Anil Annadi and B. N. Sahu of Mahindra University, Hyderabad, India for writing this review.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Dusastre, V.; Martiradonna, L. Materials for sustainable energy. *Nat. Mater.* **2017**, *16*, 15. [[CrossRef](#)]
2. Dalapati, G.K.; Chua, C.S.; Kushwaha, A.; Liew, S.L.; Suresh, V.; Chi, D. All earth abundant materials for low cost solar-driven hydrogen production. *Mater. Lett.* **2016**, *183*, 183–186. [[CrossRef](#)]
3. Jang, J.-W.; Du, C.; Ye, Y.; Lin, Y.; Yao, X.; Thorne, J.; Liu, E.; McMahon, G.; Zhu, J.; Javey, A.; et al. Enabling unassisted solar water splitting by iron oxide and silicon. *Nat. Commun.* **2015**, *6*, 7447–7452.
4. Abdel Maksoud, M.I.A.; Fahim, R.A.; Shalan, A.E.; Abd Elkodous, M.; Olojede, S.O.; Osman, A.I.; Farrell, C.; Al-Muhtaseb, A.H.; Awed, A.S.; Ashour, A.H.; et al. Advanced materials and technologies for supercapacitors used in energy conversion and storage: A review. *Environ. Chem. Lett.* **2021**, *19*, 375–439.
5. Wong, H.; Iwai, H. The road to miniaturization. *Phys. World* **2005**, *18*, 40–44. [[CrossRef](#)]
6. Lorenz, M.; Rao, M.S.R.; Venkatesan, T.; Fortunato, E.; Barquinha, P.; Branquinho, R.; Salgueiro, D.; Martins, R.; Carlos, E.; Liu, A.; et al. The 2016 oxide electronic materials and oxide interfaces roadmap. *J. Phys. D Appl. Phys.* **2016**, *49*, 433001. [[CrossRef](#)]
7. Coll, M.; Fontcuberta, J.; Althammer, M.; Bibes, M.; Boschker, H.; Calleja, A.; Cheng, G.; Cuoco, M.; Dittmann, R.; Dkhil, B.; et al. Towards oxide electronics: A roadmap. *Appl. Surf. Sci.* **2019**, *482*, 1–93.
8. Giustino, F.; Lee, J.H.; Trier, F.; Bibes, M.; Winter, S.M.; Valentí, R.; Son, Y.-W.; Taillefer, L.; Heil, C.; Figueroa, A.I.; et al. The 2021 quantum materials roadmap. *J. Phys. Mater.* **2020**, *3*, 042006. [[CrossRef](#)]
9. Fritsch, D. Electronic and optical properties of spinel zinc ferrite: Ab initio hybrid functional calculations. *J. Phys. Condens. Matter* **2018**, *30*, 095502. [[CrossRef](#)]
10. Heda, N.L.; Panwar, K.; Kumar, K.; Ahuja, B.L. Performance of hybrid functional in linear combination of atomic orbitals scheme in predicting electronic response in spinel ferrites ZnFe₂O₄ and CdFe₂O₄. *J. Mater. Sci.* **2020**, *55*, 3912–3925. [[CrossRef](#)]

11. Ulpe, A.C.; Bauerfeind, K.C.; Bredow, T. Influence of spin state and cation distribution on stability and electronic properties of ternary transition-metal oxides. *ACS Omega* **2019**, *4*, 4138–4146. [[CrossRef](#)] [[PubMed](#)]
12. Ulpe, A.C.; Bredow, T. GW-BSE calculations of electronic band gap and optical spectrum of ZnFe_2O_4 : Effect of cation distribution and spin configuration. *Chem. Phys. Chem.* **2020**, *21*, 546–551. [[CrossRef](#)] [[PubMed](#)]
13. Harris, V.G. Modern Microwave Ferrites. *IEEE Trans. Magn.* **2012**, *48*, 1075–1104. [[CrossRef](#)]
14. Lišková-Jakubisová, E.; Višňovský, Š.; Široký, P.; Hrabovský, D.; Pištora, J.; Sahoo, S.C.; Prasad, S.; Venkataramani, N.; Bohra, M.; Krishnan, R. Nanocrystalline zinc ferrite films studied by magneto-optical spectroscopy. *J. Appl. Phys.* **2015**, *117*, 17B726. [[CrossRef](#)]
15. Zviagin, V.; Kumar, Y.; Lorite, I.; Esquinazi, P.; Grundmann, M.; Schmidt-Grund, R. Ellipsometric investigation of ZnFe_2O_4 thin films in relation to magnetic properties. *Appl. Phys. Lett.* **2016**, *108*, 131901. [[CrossRef](#)]
16. Kim, J.H.; Kim, H.E.; Kim, J.H.; Lee, J.S. Ferrites: Emerging light absorbers for solar water splitting. *J. Mater. Chem. A* **2020**, *8*, 9447–9482. [[CrossRef](#)]
17. Srivastava, C.M.; Shringi, S.N.; Srivastava, R.G.; Nanadikar, N.G. Magnetic ordering and domain-wall relaxation in zinc-ferrous ferrites. *Phys. Rev. B* **1976**, *14*, 2032–2040. [[CrossRef](#)]
18. Bohra, M.; Prasad, S.; Venkataramani, N.; Sahoo, S.C.; Kumar, N.; Krishnan, R. Low temperature magnetization studies of nanocrystalline Zn-ferrite thin films. *IEEE Trans. Magn.* **2013**, *49*, 4249–4252. [[CrossRef](#)]
19. Nakashima, S.; Fujita, K.; Tanaka, K.; Hirao, K. High magnetization and the high-temperature superparamagnetic transition with intercluster interaction in disordered zinc ferrite thin film. *J. Phys. Condens. Matter.* **2005**, *17*, 137–149. [[CrossRef](#)]
20. Jedrecy, N.; Hebert, C.; Perriere, J.; Nistor, M.; Millon, E. Magnetic and magnetotransport properties of $\text{Zn}_x\text{Fe}_{3-x}\text{O}_{4-y}$ thin films. *J. Appl. Phys.* **2014**, *116*, 213903. [[CrossRef](#)]
21. Chinnasamy, C.N.; Narayanasamy, A.; Ponpandian, N.; Chattopadhyay, K.; Guérault, H.; Greneche, J.-M. Magnetic properties of nanostructured ferrimagnetic zinc ferrite. *J. Phys. Condens. Matter.* **2000**, *12*, 7795–7805. [[CrossRef](#)]
22. Hufnagel, A.G.; Peters, K.; Müller, A.; Scheu, C.; Fattakhova-Rohlfing, D.; Bein, T. Zinc ferrite photoanode nanomorphologies with favorable kinetics for water-splitting. *Adv. Funct. Mater.* **2016**, *26*, 4435–4443. [[CrossRef](#)]
23. Vadiyar, M.M.; Bhise, S.C.; Patil, S.K.; Patil, S.A.; Pawar, D.K.; Ghule, A.V.; Patil, P.S.; Kolekar, S.S. Mechanochemical growth of a porous ZnFe_2O_4 nano-flake thin film as an electrode for supercapacitor application. *RSC Adv.* **2015**, *5*, 45935–45942. [[CrossRef](#)]
24. Ding, Y.; Yang, Y.; Shao, H. High capacity ZnFe_2O_4 anode material for lithium ion batteries. *Electrochim. Acta* **2011**, *56*, 9433–9438. [[CrossRef](#)]
25. Saraf, M.; Natarajan, K.; Gupta, A.K.; Kumar, P.; Rajak, R.; Mobin, S.M. Electrochemical energy storage properties of solvothermally driven ZnFe_2O_4 microspheres. *Mater. Res. Express* **2019**, *6*, 095534. [[CrossRef](#)]
26. Kamazawa, K.; Tsunoda, Y.; Kadowaki, H.; Kohn, K. Magnetic neutron scattering measurements on a single crystal of frustrated ZnFe_2O_4 . *Phys. Rev. B* **2003**, *68*, 024412. [[CrossRef](#)]
27. Bohra, M.; Agarwal, N.; Singh, V. A short review on verwey transition in nanostructured Fe_3O_4 materials. *J. Nanomater.* **2019**, *2019*, 1–18. [[CrossRef](#)]
28. Ferrari, S.; Kumar, R.S.; Grinblat, F.; Apesteguy, J.C.; Saccone, F.D.; Errandonea, D. In-situ high-pressure x-ray diffraction study of zinc ferrite nanoparticles. *Solid State Sci.* **2016**, *56*, 68–72. [[CrossRef](#)]
29. Goodenough, J.B. *Magnetism and the Chemical Bond*; Interscience: New York, NY, USA, 1963.
30. Kanamori, J. Superexchange interaction and symmetry properties of electron orbitals. *J. Phys. Chem. Solids* **1959**, *10*, 87–98. [[CrossRef](#)]
31. Srivastava, M.; Alla, S.K.; Meena, S.S.; Gupta, N.; Mandal, R.K.; Prasad, N.K. $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ ($0.01 \leq x \leq 0.8$) nanoparticles for controlled magnetic hyperthermia application. *New J. Chem.* **2018**, *42*, 7144–7153. [[CrossRef](#)]
32. Tian, Q.; Wang, Q.; Xie, Q.; Jiangong, L. Aqueous solution preparation, structure, and magnetic properties of nano-granular $\text{Zn}_x\text{Fe}_{3-x}\text{O}_4$ ferrite films. *Nanoscale Res. Lett.* **2010**, *5*, 1518–1523. [[CrossRef](#)] [[PubMed](#)]
33. Kresse, G.; Hafner, J. Ab initio molecular-dynamics simulation of the liquid-metal–amorphous-semiconductor transition in germanium. *Phys. Rev. B* **1994**, *49*, 14251–14269. [[CrossRef](#)]
34. Kresse, G.; Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **1996**, *54*, 11169–11186. [[CrossRef](#)]
35. Csonka, G.I.; Perdew, J.P.; Ruzsinszky, A.; Philippsen, P.H.T.; Lebegue, S.; Paier, J.; Vydrov, O.A.; Ángyán, J.G. Assessing the performance of recent density functionals for bulk solids. *Phys. Rev. B* **2009**, *79*, 155107. [[CrossRef](#)]
36. Dudarev, S.L.; Botton, G.A.; Savrasov, S.Y.; Humphreys, C.J.; Sutton, A.P. Electron-energy-loss spectra and the structural stability of nickel oxide: An LSDA+U study. *Phys. Rev. B* **1998**, *57*, 1505–1509. [[CrossRef](#)]
37. Bohra, M.; Arras, R.; Bobo, J.-F.; Singh, V.; Kumar, N.; Chou, H. Multiple spintronic functionalities into single zinc-ferrous ferrite thin films. *J. Alloys Compd.* **2021**. submitted for publication.
38. Desai, M.; Prasad, S.; Venkataramani, N.; Samajdar, I.; Nigam, A.K.; Krishnan, R. Annealing induced structural change in sputter deposited copper ferrite thin films and its impact on magnetic properties. *J. Appl. Phys.* **2002**, *91*, 2220–2227. [[CrossRef](#)]
39. Bohra, M.; Prasad, S.; Kumar, N.; Misra, D.S.; Sahoo, S.C.; Venkataramani, N. Large room temperature magnetization in nanocrystalline zinc ferrite thin films. *Appl. Phys. Lett.* **2006**, *88*, 262506. [[CrossRef](#)]
40. Cobos, M.A.; Presa, P.D.L.; Llorente, I.; Alonso, J.M.; García-Escorial, A.; Marina, P.; Hernando, A.; Jiménez, J.A. Magnetic phase diagram of nanostructured zinc ferrite as a function of inversion degree δ . *J. Phys. Chem. C* **2019**, *123*, 17472–17482. [[CrossRef](#)]

41. Yao, C.; Zeng, Q.; Goya, G.F.; Torres, T.; Liu, J.; Wu, H.; Ge, M.; Zeng, Y.; Wang, Y.; Jiang, J.Z. ZnFe₂O₄ nanocrystals: Synthesis and magnetic properties. *J. Phys. Chem. C* **2007**, *111*, 12274–12278. [[CrossRef](#)]
42. Granone, L.I.; Ulpe, A.C.; Robben, L.; Klimke, S.; Jahns, M.; Renz, F.; Gesing, T.M.; Bredow, T.; Dillert, R.; Bahnemann, D.W. Effect of the degree of inversion on optical properties of spinel ZnFe₂O₄. *Phys. Chem. Chem. Phys.* **2018**, *20*, 28267–28278. [[CrossRef](#)]
43. Zviagin, V.; Sturm, C.; Esquinazi, P.D.; Grundmann, M.; Schmidt-Grund, R. Control of magnetic properties in spinel ZnFe₂O₄ thin films through intrinsic defect manipulation. *J. Appl. Phys.* **2020**, *128*, 165702. [[CrossRef](#)]
44. Marcu, A.; Yanagida, T.; Nagashima, K.; Tanaka, H.; Kawai, T. Transport properties of ZnFe₂O_{4-δ} thin films. *J. Appl. Phys.* **2007**, *102*, 023713. [[CrossRef](#)]
45. Rivero, M.; Campo, A.D.; Mayoral, Á.; Mazario, E.; Sánchez-Marcos, J.; Muñoz-Bonilla, A. Synthesis and structural characterization of Zn_xFe_{3-x}O₄ ferrite nanoparticles obtained by an electrochemical method. *RSC Adv.* **2016**, *6*, 40067–40076. [[CrossRef](#)]
46. Venkateshvaran, D.; Althammer, M.; Nielsen, A.; Geprägs, S.; Ramachandra Rao, M.S.; Sebastian, T.; Goennenwein, B.; Opel, M.; Gross, R. Epitaxial Zn_xFe_{3-x}O₄ thin films: A spintronic material with tunable electrical and magnetic properties. *Phys. Rev. B* **2009**, *79*, 134405. [[CrossRef](#)]
47. Sahu, B.N.; Venkataramani, N.; Prasad, S.; Krishnan, R. Effect of thickness on magnetic and microwave properties of RF-sputtered Zn-ferrite thin films. *AIP Adv.* **2017**, *7*, 056102.
48. Hwang, H.; Shin, H.; Lee, W.-J. Effects of calcination temperature for rate capability of triple-shelled ZnFe₂O₄ hollow microspheres for lithium ion battery anodes. *Sci. Rep.* **2017**, *7*, 46378. [[CrossRef](#)]
49. Takaobushi, J.; Tanaka, H.; Kawai, T.; Ueda, S.; Kim, J.-J.; Kobata, M.; Ikenaga, E.; Yabashi, M.; Kobayashi, K.; Nishino, Y.; et al. Fe_{3-x}Zn_xO₄ thin film as tunable high Curie temperature ferromagnetic semiconductor. *Appl. Phys. Lett.* **2006**, *89*, 242507. [[CrossRef](#)]
50. Yamamoto, Y.; Tanaka, H.; Kawai, T. The control of cluster-glass transition temperature in spinel-type ZnFe₂O_{4-δ} thin film. *Jpn. J. Appl. Phys.* **2001**, *40*, L545–L547. [[CrossRef](#)]
51. Lorenz, M.; Brandt, M.; Mexner, K.; Brachwitz, K.; Ziese, M.; Esquinazi, P.; Hochmuth, H.; Grundmann, M. Ferrimagnetic ZnFe₂O₄ thin films on SrTiO₃ single crystals with highly tunable electrical conductivity. *Phys. Status Solidi RRL* **2011**, *5*, 438–440. [[CrossRef](#)]
52. Saha, P.; Rakshit, R.; Alam, M.; Mandal, K. Magnetic and electronic properties of Zn doped Fe₃O₄ hollow nanospheres. *Phys. Rev. Appl.* **2019**, *11*, 024059–024069. [[CrossRef](#)]
53. Bohra, M.; Prasad, S.; Venkataramani, N.; Kumar, N.; Sahoo, S.C.; Krishnan, R. Narrow ferromagnetic resonance line width polycrystalline Zn-ferrite thin films. *IEEE Trans. Magn.* **2011**, *47*, 345–348. [[CrossRef](#)]
54. Sai, R.; Endo, Y.; Shimada, Y.; Yamaguchi, M.; Shivashankar, S.A. Oriented nanometric aggregates of partially inverted zinc ferrite: One-step processing and tunable high-frequency magnetic properties. *J. Appl. Phys.* **2015**, *117*, 17E511.
55. Sai, R.; Shivashankar, S.A.; Yamaguchi, M.; Bhat, N. Magnetic nanoferrites for RF CMOS: Enabling 5G and beyond. *Electrochem. Soc. Interface* **2017**, *26*, 71–76.
56. Sai, R.; Vinoy, K.J.; Bhat, N.; Shivashankar, S.A. CMOS-compatible and scalable deposition of nanocrystalline zinc ferrite thin film to improve inductance density of integrated RF inductor. *IEEE Trans. Magn.* **2013**, *49*, 4323–4326.
57. Ameer, S.; Gul, I.H.; Mahmood, N.; Mujahid, M. Semiconductor-to-metallic flipping in a ZnFe₂O₄-graphene based smart nano-system: Temperature/microwave magneto-dielectric spectroscopy. *Mater. Charact.* **2015**, *99*, 254–265. [[CrossRef](#)]
58. Shi, R.; Zhang, Y.; Wang, X.; Ma, Q.; Zhang, A.; Yang, P. Electrospun ZnFe₂O₄ nanotubes and nanobelts: Morphology evolution, formation mechanism and Fenton-like photocatalytic activities. *Mater. Chem. Phys.* **2018**, *207*, 114–122.
59. Wang, K.; Zhan, S.; Sun, H.; Zhang, D.; Wang, J. Hollow porous core-shell ZnFe₂O₄/AgCl nanocubes coated with EDTA and Ag nanoparticles for enhanced photocatalytic performances of visible-light-driven. *Chem. Eng. J.* **2020**, *400*, 125908.
60. Sahoo, S.C.; Venkataramani, N.; Prasad, S.; Bohra, M.; Krishnan, R. Magnetic Properties of Nanocrystalline CoFe₂O₄/ZnFe₂O₄ Bilayers. *J. Supercond. Nov. Magn.* **2012**, *25*, 2653–2657. [[CrossRef](#)]
61. Wu, Q.; Yu, Z.; Wu, Y.; Gao, Z.; Xie, H. The magnetic and photocatalytic properties of nanocomposites SrFe₁₂O₁₉ /ZnFe₂O₄. *J. Magn. Magn. Mater.* **2018**, *465*, 1–8.
62. Taiping, X.; Longjun, X.; Chenglun, L.; Yuan, W. Magnetic composite ZnFe₂O₄/SrFe₁₂O₁₉: Preparation, characterization, and photocatalytic activity under visible light. *Appl. Surf. Sci.* **2013**, *273*, 684–691.
63. Bohra, M.; Singh, V.; Sowwan, M.; Bobo, J.-F.; Chung, C.-J.; Clemens, B. Influence of packaging on the surface oxidation and magnetic properties of cobalt nanocrystals. *J. Phys. D Appl. Phys.* **2014**, *47*, 305002. [[CrossRef](#)]
64. Lin, W.-J.; Chang, W.-C.; Qi, X. Exchange bias and magneto-resistance in an all-oxide spin valve with multi-ferroic BiFeO₃ as the pinning layer. *Acta Mater.* **2013**, *61*, 7444–7453. [[CrossRef](#)]
65. Gao, X.; Wang, J.; Zhang, D.; Adair, K.; Feng, K.; Sun, N.; Zheng, H.; Shao, H.; Zhong, J.; Ma, Y. Carbon coated bimetallic sulfide nanodots/carbon nanorod heterostructure enabling long-life lithium-ion batteries. *J. Mater. Chem.* **2017**, *5*, 25625–25631. [[CrossRef](#)]
66. Hou, L.; Lian, L.; Zhang, L.; Pang, G.; Yuan, C.; Zhang, X. Self-sacrifice template fabrication of hierarchical mesoporous Bi-component-active ZnO/ZnFe₂O₄ sub-microcubes as superior anode towards high-performance lithium-ion battery. *Adv. Funct. Mater.* **2015**, *25*, 238–246. [[CrossRef](#)]
67. Yu, S.-H.; Lee, S.H.; Lee, D.J.; Sung, Y.-E.; Hyeon, T. Conversion reaction-based oxide nanomaterials for lithium ion battery anodes. *Small* **2016**, *12*, 2146–2172. [[CrossRef](#)]

68. Yuan, C.; Wu, H.B.; Xie, Y.; Lou, X.W. Mixed transition-metal oxides: Design, synthesis, and energy-related applications. *Angew. Chem. Int. Ed. Engl.* **2014**, *53*, 1488–1504.
69. Lu, G.; Qiu, S.; Liu, J.; Wang, X.; He, C.; Bai, Y.J. Enhanced electrochemical performance of Zn-doped Fe₃O₄ with carbon coating. *Electrochim. Acta* **2014**, *117*, 230–238. [[CrossRef](#)]
70. Guo, X.; Lu, X.; Fang, X.; Mao, Y.; Wang, Z.; Chen, L.; Xu, X.; Yang, H.; Liu, Y. Lithium storage in hollow spherical ZnFe₂O₄ as anode materials for lithium ion batteries. *Electrochem. Commun.* **2010**, *12*, 847–850. [[CrossRef](#)]
71. Bresser, D.; Paillard, E.; Kloepsch, R.; Krueger, S.; Fiedler, M.; Schmitz, R.; Baither, D.; Winter, M.; Passerini, S. Carbon coated ZnFe₂O₄ nanoparticles for advanced lithium-ion anodes. *Adv. Energy Mater.* **2013**, *3*, 513–523. [[CrossRef](#)]
72. Teh, P.F.; Pramana, S.S.; Kim, C.; Chen, C.M.; Chuang, C.H.; Sharma, Y.; Cabana, J.; Madhavi, S. Electrochemical reactivity with lithium of spinel-type ZnFe_{2–y}Cr_yO₄ (0 ≤ y ≤ 2). *J. Phys. Chem. C* **2013**, *117*, 24213–24223.
73. Bourrioux, S. Laser-Pyrolysed ZnFe₂O₄ Anode for Lithium-Ion Batteries: Understanding of the Lithium Storage Mechanisms. Ph.D. Thesis, Université Grenoble Alpes and NTU Singapore, Singapore, 2018.
74. Zhang, Y.; Pelliccione, C.J.; Brady, A.B.; Guo, H.; Smith, P.F.; Liu, P.; Marschilok, A.C.; Takeuchi, K.J.; Takeuchi, E.S. Probing the Li insertion mechanism of ZnFe₂O₄ in Li-ion batteries: A combined X-ray diffraction, extended X-ray absorption fine structure, and density functional theory study. *Chem. Mater.* **2017**, *29*, 4282–4292. [[CrossRef](#)]
75. Guo, H.; Zhang, Y.; Marschilok, A.C.; Takeuchi, K.J.; Takeuchi, E.S.; Liu, P. A first principles study of spinel ZnFe₂O₄ for electrode materials in lithium-ion batteries. *Phys. Chem. Chem. Phys.* **2017**, *19*, 26322–26329. [[CrossRef](#)] [[PubMed](#)]
76. Wang, Z.; Liang, Z.; Xiong, W.L. Metal oxide hollow nanostructures for lithium ion batteries. *Adv. Mater.* **2012**, *24*, 1903–1911.
77. Hou, X.; Wang, X.; Yao, L.; Hu, S.; Wu, Y.; Liu, X. Facile synthesis of ZnFe₂O₄ with inflorescence spicate architecture as anode materials for lithium-ion batteries with outstanding performance. *New J. Chem.* **2015**, *39*, 1943–1952. [[CrossRef](#)]
78. Nuli, Y.N.; Chu, Y.Q.; Qin, Q.Z. Nanocrystalline ZnFe₂O₄ and Ag-doped ZnFe₂O₄ films used as new anode materials for Li-ion batteries. *J. Electrochem. Soc.* **2003**, *151*, A1077–A1083. [[CrossRef](#)]
79. Sharma, Y.; Sharma, N.; Rao, G.V.S.; Chowdari, B.V.R. Li-storage and cyclability of urea combustion derived ZnFe₂O₄ as anode for li-ion batteries. *Electrochim. Acta* **2008**, *53*, 2380–2385. [[CrossRef](#)]
80. Pei, F.T.; Sharma, Y.; Pramana, S.S.; Srinivasan, M. Nanoweb anodes composed of one-dimensional, high aspect ratio, size tunable electrospun ZnFe₂O₄ nanofibers for lithium ion batteries. *J. Mater. Chem.* **2011**, *21*, 14999–15008.
81. Xing, Z.; Ju, Z.; Yang, J. One-step hydrothermal synthesis of ZnFe₂O₄ nano-octahedrons as a high capacity anode material for Li-ion batteries. *Nano Res.* **2012**, *5*, 477–485. [[CrossRef](#)]
82. Zhong, X.B.; Yang, Z.Z.; Wang, H.Y.; Lu, L.; Jin, B.; Zha, M.; Jiang, Q.C. A novel approach to facilely synthesize mesoporous ZnFe₂O₄ nanorods for lithium ion batteries. *J. Power Source* **2016**, *306*, 718–723. [[CrossRef](#)]
83. Zhong, X.B.; Jin, B.; Yang, Z.Z.; Wang, C.; Wang, H.Y. Facile shape design and fabrication of ZnFe₂O₄ as an anode material for Li-ion batteries. *RSC Adv.* **2014**, *4*, 55173–55178. [[CrossRef](#)]
84. Fang, Z.; Zhang, L.; Qi, H.; Yue, H.; Zhang, T.; Zhao, X.; Chen, G.; Wei, Y.; Wang, C.; Zhang, D. Nanosheet assembled hollow ZnFe₂O₄ microsphere as anode for lithium-ion batteries. *J. Alloy. Compd.* **2018**, *762*, 480–487. [[CrossRef](#)]
85. Yu, M.; Huang, Y.; Wang, K.; Han, X.; Wang, M.; Zhu, Y.; Liu, L. Complete hollow ZnFe₂O₄ nanospheres with huge internal space synthesized by a simple solvothermal method as anode for lithium ion batteries. *Appl. Surf. Sci.* **2018**, *462*, 955–962. [[CrossRef](#)]
86. Zhang, M.; Liu, Y.; Zhu, H.; Wang, X. Hierarchical bead chain ZnFe₂O₄-PEDOT composites with enhanced Li-ion storage properties as anode materials for lithium-ion batteries. *Appl. Surf. Sci.* **2020**, *529*, 147078. [[CrossRef](#)]
87. Roger, I.; Shipman, M.A.; Symes, M.D. Earth-abundant catalysts for electrochemical and photoelectrochemical water splitting. *Nat. Rev. Chem.* **2017**, *1*, 1–13.
88. Polo, A.; Lhermitte, C.R.; Dozzi, M.V.; Selli, E.; Sivula, K. Hydrogenation of ZnFe₂O₄ flat films: Effects of the pre-annealing temperature on the photoanodes efficiency for water oxidation. *Surfaces* **2020**, *3*, 9. [[CrossRef](#)]
89. Kim, J.H.; Jang, Y.J.; Choi, S.H.; Lee, B.J.; Kim, J.H.; Park, Y.B.; Nam, C.M.; Kim, H.G.; Lee, J.S. A multitude of modifications strategy of ZnFe₂O₄ nanorod photoanodes for enhanced photoelectrochemical water splitting activity. *J. Mater. Chem. A* **2018**, *6*, 12693–12700. [[CrossRef](#)]
90. Kim, J.H.; Kim, J.H.; Jang, J.W.; Kim, J.Y.; Choi, S.H.; Magesh, G.; Lee, J.; Lee, J.S. Awakening solar water-splitting activity of ZnFe₂O₄ nanorods by hybrid microwave annealing. *Adv. Energy Mater.* **2014**, *5*, 1401933. [[CrossRef](#)]
91. Lan, Y.; Liu, Z.; Guo, Z.; Ruan, M.; Li, X. A promising p-type Co-ZnFe₂O₄ nanorod film as a photocathode for photoelectrochemical water splitting. *Chem. Commun.* **2020**, *56*, 5279–5282. [[CrossRef](#)]
92. Guo, Y.; Zhang, N.; Wang, X.; Qian, Q.; Zhang, S.; Li, Z.; Zou, Z. A facile spray pyrolysis method to prepare Ti-doped ZnFe₂O₄ for boosting photoelectrochemical water splitting. *J. Mater. Chem. A* **2017**, *5*, 7571–7577. [[CrossRef](#)]
93. Sahu, T.K.; Shah, A.K.; Gogoi, G.; Patra, A.S.; Ansari, M.S.; Qureshi, M. Effect of surface overlayer in enhancing the photoelectrochemical water oxidation of in-situ grown one dimensional spinel zinc ferrite nanorods directly onto the substrate. *Chem. Commun.* **2018**, *54*, 10483–10486. [[CrossRef](#)]
94. Guijarro, N.; Bornoz, P.; Prévot, M.; Yu, X.; Zhu, X.; Johnson, M.; Jeanbourquin, X.; Formal, F.L.; Sivula, K. Evaluating spinel ferrites MFe₂O₄ (M = Cu, Mg, Zn) as photoanodes for solar water oxidation: Prospects and limitations. *Sustain. Energy Fuels* **2018**, *2*, 103–117. [[CrossRef](#)]
95. Zhu, X.; Guijarro, N.; Liu, Y.; Schouwink, P.; Wells, R.A.; Formal, F.L.; Sun, S.; Gao, C.; Sivula, K. Spinel structural disorder influences solar-water-splitting performance of ZnFe₂O₄ nanorod photoanodes. *Adv. Mater.* **2018**, *30*, 1801612. [[CrossRef](#)]

96. Zhang, D.; Li, W.; Ye, R.; Guo, X.; Wang, S.; Wang, X.; Xiang, Q. A facile strategy for ZnFe₂O₄ coating preparing by electrophoretic deposition and its supercapacitor performances. *J. Mater. Sci. Mater. Electron.* **2018**, *29*, 5454–5458. [[CrossRef](#)]
97. Israr, M.; Iqbal, J.; Arshad, A.; Aisida, S.O.; Ahmad, I. A unique ZnFe₂O₄/graphene nanoplatelets nanocomposite for electrochemical energy storage and efficient visible light driven catalysis for the degradation of organic noxious in wastewater. *J. Phys. Chem. Solids* **2020**, *140*, 109333. [[CrossRef](#)]
98. Javed, M.S.; Jiang, Z.; Yang, Q.; Wang, X.; Han, X.; Zhang, C.; Gu, X.; Hu, C. Exploring Li-ion hopping behaviour in zinc ferrite and promoting performance for flexible solid-state supercapacitor. *Electrochem. Acta* **2019**, *295*, 558–568. [[CrossRef](#)]
99. Vadiyar, M.M.; Kolekar, S.S.; Chang, J.Y.; Ye, Z.; Ghule, A.V. Anchoring ultrafine ZnFe₂O₄/C nanoparticles on 3D ZnFe₂O₄ nanoflakes for boosting cycle stability and energy density of flexible asymmetric supercapacitor. *ACS Appl. Mater. Interfaces* **2017**, *9*, 26016–26028. [[CrossRef](#)] [[PubMed](#)]