



# Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization

Oleg Lupan, Nicolai Ababii, David Santos-Carballal, Maik-Ivo Terasa, Nicolae Magariu, Dario Zappa, Elisabetta Comini, Thierry Pauporté, Leonard Siebert, Franz Faupel, et al.

## ► To cite this version:

Oleg Lupan, Nicolai Ababii, David Santos-Carballal, Maik-Ivo Terasa, Nicolae Magariu, et al.. Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. *Nano Energy*, 2021, 88, pp.106241. 10.1016/j.nanoen.2021.106241 . hal-03367679

**HAL Id: hal-03367679**

**<https://hal.science/hal-03367679>**

Submitted on 6 Oct 2021

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

## **Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization**

Oleg Lupan <sup>a,b,c,d,\*</sup>, Nicolai Ababii <sup>b</sup>, David Santos-Carballal <sup>e,\*</sup>, Maik-Ivo Terasa <sup>a</sup>, Nicolae Magariu <sup>b</sup>, Dario Zappa <sup>f</sup>, Elisabetta Comini <sup>f</sup>, Thierry Pauporte <sup>d</sup>, Leonard Siebert <sup>a</sup>, Franz Faupel <sup>g,\*</sup>, Alexander Vahl <sup>g,\*</sup>, Sandra Hansen <sup>a,\*</sup>, Nora H de Leeuw <sup>e,h</sup>, and Rainer Adelung <sup>a,\*</sup>

<sup>a</sup> *Functional Nanomaterials, Faculty of Engineering, Institute for Materials Science, Kiel University, Kaiserstr. 2, D-24143, Kiel, Germany*

<sup>b</sup> *Center for Nanotechnology and Nanosensors, Department of Microelectronics and Biomedical Engineering, Technical University of Moldova, 168 Stefan cel Mare Av., MD-2004 Chisinau, Republic of Moldova*

<sup>c</sup> *Department of Physics, University of Central Florida, Orlando, FL 32816-2385, USA*

<sup>d</sup> *PSL Université, Institut de Recherche de Chimie Paris-IRCP, Chimie ParisTech, rue Pierre et Marie Curie 11, 75231 Paris Cedex 05, France*

<sup>e</sup> *School of Chemistry, University of Leeds, Leeds LS2 9JT, United Kingdom*

<sup>f</sup> *Sensor Laboratory, Department of Information Engineering (DII), University of Brescia, Via Branze 38, Brescia 25123, Italy*

<sup>g</sup> *Chair for Multicomponent Materials, Faculty of Engineering, Kiel University, Kaiserstr. 2, D-24143, Kiel, Germany*

<sup>h</sup> *Department of Earth Sciences, Utrecht University, Princetonplein 8A, 3584 CD Utrecht, The Netherlands*

\*Corresponding authors:

Rainer Adelung ([ra@tf.uni-kiel.de](mailto:ra@tf.uni-kiel.de)),

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

Oleg Lupan ([ollu@tf.uni-kiel.de](mailto:ollu@tf.uni-kiel.de) , [oleg.lupan@mib.utm.md](mailto:oleg.lupan@mib.utm.md)), Dr. David Santos-Carballal ([d.santos-carballal@leeds.ac.uk](mailto:d.santos-carballal@leeds.ac.uk)) Dr. Alexander Vahl ([alva@tf.uni-kiel.de](mailto:alva@tf.uni-kiel.de)), Dr. Sandra Hansen ([sn@tf.uni-kiel.de](mailto:sn@tf.uni-kiel.de))

**Keywords:** Nanolayered materials, heterojunctions, semiconductor oxides, gas sensing, low-energy, ultralow power

## **Abstract**

**Heterojunctions are used in solar cells and optoelectronics applications owing to their excellent electrical and structural properties. Recently, these energy-efficient systems have also been employed as sensors to distinguish between individual gases within mixtures. Through a simple and versatile functionalization approach using noble metal nanoparticles, the sensing properties of heterojunctions can be controlled at the nanoscopic scale. This work reports the nanoparticle surface functionalization of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O mixed oxide heterostructures, where the gas sensing selectivity of the material is tuned to achieve versatile sensors with ultra-low power consumption. Functionalization with Ag or AgPt-nanoclusters (5-15 nm diameter), changed the selectivity from ethanol to butanol vapour. The Pd-nanocluster functionalization shifts the selectivity from the alcohols to hydrogen. The fabricated sensors show excellent low power consumption below 1 nW. To gain insight into the selectivity mechanism, density functional theory (DFT) calculations were carried out to simulate the adsorption of H<sub>2</sub>, C<sub>2</sub>H<sub>5</sub>OH and *n*-C<sub>4</sub>H<sub>9</sub>OH at the noble metal nanoparticle decorated ternary heterostructure interface. These calculations also show a decrease in the work function by ~2.6 eV with respect to the pristine ternary heterojunctions. This work lays the foundation for the production of a very versatile array of sensors of ultra-low power consumption with applications for the detection of individual gases in a mixture.**

## **1. Introduction**

Tuning the properties of semiconductor-powered devices by means of functional oxide nanomaterials is a state-of-the-art technological approach. Heterojunctions have gained attention for applications in optoelectronics and solar cells, but they can also be employed as versatile and excellent ultra-low power gas sensors owing to the high degree of phase control at the nanoscopic level [1–6]. Previous studies on the decoration of semiconducting metal oxide nanostructures with nanoparticles (NPs), have demonstrated the versatile nature of such combined systems, e.g. in gas, UV and temperature sensors or for the discrimination of volatiles [7–9]. For example, a significant increase in sensitivity by a factor of ~ 60 and selectivity towards 200 ppm of ethanol vapors was achieved following surface functionalization of columnar ZnO:Fe films using AgO/Ag nanoparticles [4], which was confirmed by quantum mechanical calculations showing that (AgO)<sub>5</sub> clusters change the surface chemistry of the Fe-doped zinc oxide ZnO (10-10) surface towards ethanol detection [4]. Wang *et al.* [10] found that tetragonal rutile SnO<sub>2</sub> nanosheets decorated with an optimum amount of 3 mol% of NiO nanoparticles increases by five times the response to 100 ppm of C<sub>2</sub>H<sub>5</sub>OH at 260 °C, compared to the sensor containing only pure SnO<sub>2</sub> nanosheets. These findings were assigned to the formation of a *p–n* junction between the NiO nanoparticles and SnO<sub>2</sub> nanosheets [10]. Moreover, surface functionalisation using nanoparticles of noble metals and their alloys has been used previously to fabricate sensors for the detection of VOC molecules [9,11]. Titanium dioxide (TiO<sub>2</sub>) nanometer-sized quantum dots (QDs) have been grown by Liu and co-workers, who found that Ag decoration led to a 6-fold increase in the sensing response toward 10–100 ppm NH<sub>3</sub> gas at room temperature [12]. Moreover, Wu *et al.* [13] found that for in-situ electrochemical activation by the surface/interface modulation and to enhance the catalytic performances of nanomaterials, novel bi-functional sandwich-like electrocatalysts of FeCo<sub>2</sub>O<sub>4</sub>@FeCo<sub>2</sub>S<sub>4</sub>@PPy or MCo<sub>2</sub>O<sub>4</sub>@MCo<sub>2</sub>S<sub>4</sub>@PPy can be used, which reveals that the bi-product interface can motivate more active sites than a single nanomaterials interface [13–16].

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

Some advantages of noble metal modified nanoparticles compared with pure precious metal catalysts are: the deposition time of nanoparticles is quite small, the density of nanoparticles can be directed only with the deposition time and no precursor solutions need to be prepared.

An excellent example for the requirement of reliable gas sensors is *n*-butanol, which is a stimulating and narcotic volatile compound, used extensively as a solvent and extracting agent of organic synthesis intermediates [17]. However, exposure to *n*-butanol vapours has adverse health effects in humans, causing symptoms like dizziness, headaches, somnolence or dermatitis [7,17,18]. The traditional and most frequently used method for the detection of *n*-butanol is gas chromatography (GC) [17,19,20], which is a complicated, time-consuming and costly technique. The current trend of developing solid state gas sensors of low energy consumption, has led to the use of metal oxide semiconductors as good candidates to fabricate highly sensitive, selective and reliable *n*-butanol gas sensors [4,17,21].

Given that one of the important advantages to improve the highly selective sensitivity for certain specific gases and VOCs is the functionalization of the semiconducting metal oxide nanostructures surfaces with different types of noble metals [6], this study reports the fabrication of gas sensors for VOCs and H<sub>2</sub> using a titania/cupric oxide/cuprite (TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O/glass) heterostructure decorated with noble metal nanoparticles. To gain insight into the sensing mechanism, we also present calculations based on the density functional theory (DFT) of the ternary heterojunction TiO<sub>2</sub>(111)/CuO( $\bar{1}\bar{1}\bar{1}$ )/Cu<sub>2</sub>O(111) decorated with Pd<sub>7</sub>, Ag<sub>7</sub> and Ag<sub>6</sub>Pt nanoparticles, where we calculate the adsorption energies, structures and work functions after impregnation with the noble metal nanoclusters. Despite the lattice mismatch introduced by the deposition of the monoclinic CuO( $\bar{1}\bar{1}\bar{1}$ ) and TiO<sub>2</sub>(111) thin film overlayers on the Cu<sub>2</sub>O(111) surface substrate with hexagonal symmetry, this is a thermodynamically stable heterostructure [22,23]. The change of selectivity of the sensors is investigated by examining the binding energies and charge transfers for the interactions of molecular hydrogen (H<sub>2</sub>), ethanol (C<sub>2</sub>H<sub>5</sub>OH) and *n*-

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

butanol ( $n\text{-C}_4\text{H}_9\text{OH}$ ) with the heteroepitaxial junctions functionalized by the noble metal nanoparticles.

This work demonstrates that the introduction of noble metal nanoparticles on the surface of  $\text{TiO}_2/\text{CuO}/\text{Cu}_2\text{O}$  presents a suitable route towards developing gas sensing devices with ultra-low energy consumption. The nanoscopic scale of the functionalisation also allows tuning, modulating and controlling the selectivity and response of these sensors, which can be used for practical applications requiring the discrimination between different VOCs and  $\text{H}_2$  gas.

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

## **2. Methods**

### **2.1 Experimental**

Synthesis of the CuO-Cu<sub>2</sub>O ultra-thin layers (20-60 nm of thickness) was achieved by sputtering an ultra-thin film of copper metal (Cu film with 20, 30, 40, 50 and 60 nm thicknesses) on top of a clean glass under vacuum conditions. The glass samples coated with the ultra-thin film of copper metal were thermally treated at 420°C in an electrical furnace for 30 or 60 min under normal ambient conditions, because in the range of temperatures of 350°C and 450°C the mixed crystal phases of CuO/Cu<sub>2</sub>O are formed [22,24]. Next, titania (TiO<sub>2</sub>) films of 20 nm thick were spray-deposited on top of the layers of the mixed copper oxide phases, thus preparing six additional sample sets. Afterwards, the samples of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O heterostructure were treated in air at 420°C for another 30 min (for the Cu<sub>20</sub>, Cu<sub>30</sub>, Cu<sub>40</sub> samples) or 60 min (for the Cu<sub>50</sub>, Cu<sub>60</sub> samples), depending on their thickness, before allowing them to cool down to room temperature. The next step comprised the sputtering of Au top-contacts on the surface of the fabricated TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples by means of a meander-shaped mask. The TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O thin films were decorated with Ag and AgPt alloy nanoparticles (Ag NP and AgPt NP) using a high vacuum deposition system (custom-made) with attached Gas Aggregation Source (GAS, Haberland type [25]). Details of the deposition of noble metal alloy nanoparticles can be found in our earlier work [7,26]. For the preparation of thin film composites with Pd NPs, a similar custom-constructed chamber for deposition under high vacuum and with attached Haberland-type GAS was used [9,11,27] and a technological approach developed by Lupan et al. [28].

A TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O nanocomposite thin film, decorated with AgPt NPs, was investigated using X-ray photoelectron spectroscopy (XPS, Omicron Nano-Technology GmbH, Al, 240 W). The obtained XPS data were charge referenced with respect to aliphatic carbon C1s at 285.0 eV and analysed (“CasaXPS, version 2.3.16”) [9,11,27].



*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

For the electrical studies, different bias voltages were applied to the functionalized samples and measurements were taken continuously and registered using a computer-controlled Keithley2400 sourcemeter using the LabView software (National Instruments). The gas response was determined as the ratio ( $\frac{R_g - R_a}{R_a} \cdot 100\%$ ), where  $R_g$  and  $R_a$  stand for the resistance of the device structures exposed to gas or air, accordingly [22,29].

The general technological flow process for the manufacture of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O heterostructure-based sensor devices, which is represented in Figure 1, consists of surface functionalization using Pd, Ag or AgPt nanoparticles. In the insert of Figure 1 is represented a cross-sectional structure of the multilayered devices comprising the Pd-, Ag- or AgPt-NPs/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O systems.

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

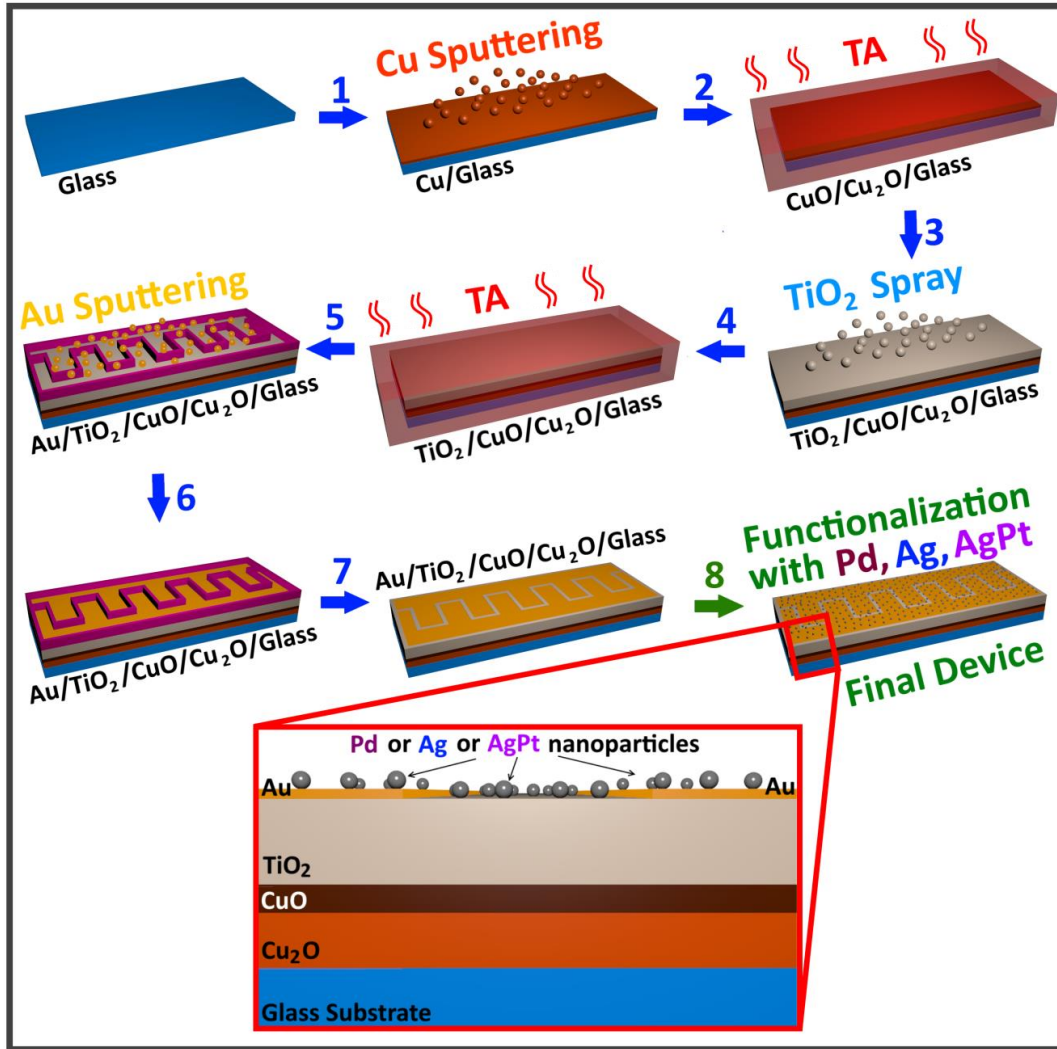


Fig. 1. (a) The technological flowchart for the manufacture of sensor device structures based on nanostructured layered films consisting of Pd, Ag or AgPt NPs on top of TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Final device structure). Cross-section view of a device based on Pd, Ag or AgPt NPs on top of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O -based sensor in insert from (a).

## 2.2 Computational

We have used the Vienna Ab initio Simulation Package (VASP) [30–33] to carry out spin-polarized calculations within the usual Kohn-Sham (KS) implementation of the density

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

functional theory (DFT). The generalized gradient approximation (GGA) was employed with the Perdew, Burke and Ernzerhof (PBE) functional for the exchange-correlation energy [34,35]. Long-range dispersion interactions were included using the semi-empirical method of Grimme, with the Becke-Johnson damping [D3-(BJ)] [36,37], which is required for the realistic simulation of the bulk and surface properties of several different materials [9,38–45]. The inner electron included up to the 3s level for Cu; 2p level for Ti; 4f level for Pt; 4s level for Pd and Ag; and 1s level for O, C and N, and were described by the projector augmented wave (PAW) method [46,47], whereas the electron of the H atom was treated as valence. The valence states were expanded in a periodic plane-wave basis set with a cut off at 400 eV for the kinetic energy. An energy threshold defining self-consistency of the electron density was set at  $10^{-5}$  eV. An efficient conjugate-gradients technique based on the Newton line optimizer [48,49] was used for the relaxation of the geometries, which reached the ground state when the Hellmann-Feynman forces on all atoms were smaller than  $0.01 \text{ eV} \cdot \text{\AA}^{-1}$ . We have used the Hubbard approximation [50] in the form of the Dudarev *et al.* [51] scheme to improve the description of localized *d* states in this type of system, where the standard GGA functionals fail [52]. The values for the on-site Coulomb interaction term in this study were  $U_{\text{eff}} = 4.0 \text{ eV}$  for Cu and  $4.4 \text{ eV}$  for Ti [22,23,53–57]. However, no Hubbard Hamiltonian was applied to the *d* states of the noble metal NPs, as they are already delocalised given the electron conducting properties of these materials [58,59]. These criteria allowed convergence of the total electronic energy to within  $1 \text{ meV} \cdot \text{atom}^{-1}$ .

The electronic integrations of the face-centred cubic (*fcc*) transition metal phases were calculated in the reciprocal space using their primitive unit cells and a  $\Gamma$ -centred Monkhorst-Pack (MP) sampling grid [60] containing  $17 \times 17 \times 17$  *k*-points, which was sufficient to simulate correctly their conducting electronic properties [58,59]. The nanoparticle-functionalised  $\text{TiO}_2(111)/\text{CuO}(\bar{1}\bar{1}\bar{1})/\text{Cu}_2\text{O}(111)$  heterostructure was simulated using a  $\Gamma$ -centred MP mesh [60] of  $5 \times 5 \times 1$  *k*-points, in line with previous

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

works [22,23]. The isolated molecules were modelled in a cell with broken symmetry and dimensions of  $20 \times 21 \times 22 \text{ \AA}^3$ , considering only the  $\Gamma$  point of the Brillouin zone. The electronic partial occupancies of the isolated molecules were determined using the Gaussian smearing method with a smearing width of 0.05 eV. The method of Methfessel-Paxton order 1 with a sigma value of  $\sigma = 0.2 \text{ eV}$  was applied to the *fcc* metal phases [61], which ensured a negligible variational quantity, *i.e.* electronic entropy [62]. Moreover, the tetrahedron method with Blöchl corrections [63] was used for the calculation of the electronic and magnetic properties and to obtain very accurate total energies for the nanoparticle functionalised heteroepitaxial junctions before and after molecular adsorption of the gases.

### 3. Results and Discussion

#### 3.1 Morphological evolutions and composition analysis

Scanning electron microscope (SEM) images are presented in Figure 2 for the mixed copper oxide CuO/Cu<sub>2</sub>O substrate coated with a TiO<sub>2</sub> layer and functionalised with the Pd, Ag and AgPt noble metal nanoparticles. The surface of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O material is covered with nanoclusters of 5-15 nm in diameter, which are forming uniformly interconnected nano-crystallites, which is favourable for sensor device applications. The SEM images of the CuO/Cu<sub>2</sub>O, TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O and AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples are shown in Figures S1. To better understand the structures, the SEM images at high and low magnification are represented in Figures S2 and S3 in the Supporting Information.

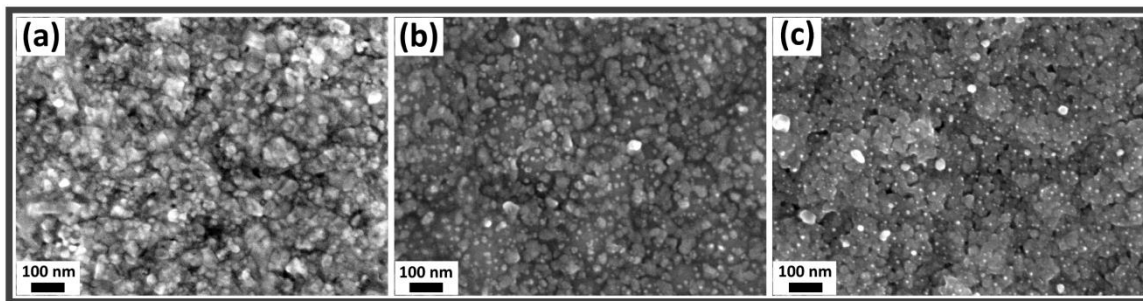


Fig. 2. Higher magnification of SEM images of interconnected nano-crystallite TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O covered with: (a) Pd nanoparticles, Cu20 set samples; (b) Ag nanoparticles, Cu60 set samples; (c) AgPt nanoparticles, Cu60 set samples, nanoclusters of 5-15 nm in diameter.

#### 3.2 X-ray photoelectron spectroscopy, Micro-Raman and UV-Visible-NIR spectroscopy characterization of CuO/Cu<sub>2</sub>O and TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O nanocomposite

The X-ray photoelectron spectra (XPS) of a TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O nanocomposite decorated with AgPt NPs are shown in Figure 3. Cu, O, Ti, Na and C elements were detected in both the nanocomposite as well as in the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O reference thin film, see the overview spectra in Figure 3a. The presence of Cu, O and Ti originates from the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O base layer, although the signal from carbon is due to contamination of the top surface with C from the atmosphere, e.g. from carbohydrates [9,11,27]. The observation of the signal corresponding to Na is due to diffusion from the glass substrates, which were used for the

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

deposition of the sensor structures [7,64,65]. Such peaks were not detected from samples deposited on quartz substrates (not shown here).

Figure 3b depicts the high-resolution spectra of the Cu-2p, Ti-2p, Ag-3d and Pt-4d lines. A closer look at the Cu-2p line reveals clear satellite peaks for both the Cu-2p<sub>3/2</sub> and Cu-2p<sub>1/2</sub> lines, which are relocated to higher binding energies. The Cu-2p<sub>3/2</sub> line, as well as the corresponding satellites, were assigned to the nanocomposite – see deconvolution of 2p<sub>3/2</sub> with satellite peaks into 3 subpeaks. The observed satellite peaks are generally regarded as a signature for the occurrence of the CuO/Cu<sub>2</sub>O heterojunction with CuO exposed at the surface [8,9]. Accordingly, the signal from copper in the spectrum can be assigned to the existence of CuO/Cu<sub>2</sub>O in the base layer.

A Ti-2p<sub>3/2</sub> peak in the range 459.6 eV - 458.0 eV is usually assigned to Ti<sup>4+</sup> in TiO<sub>2</sub>. The evaluation of high resolution Ti-2p XPS binding energies reveals that the Ti-2p<sub>3/2</sub> line is positioned around 458.3 eV. The peak positions of Ti-2p<sub>3/2</sub> and Ti-2p<sub>1/2</sub> and their separation of 5.6 eV indicate the presence of Ti in the form of TiO<sub>2</sub> in the base layer [66,67].

Ag and Pt were detected alongside Cu, Ti, O and C in the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O nanocomposite decorated using the AgPt NPs. Spectra at higher resolution of the Ag-3d and Pt-4d lines were recorded in order to evaluate the composition of the AgPt NPs. We chose the Pt-4d lines for quantification due to the overlap of Pt-4f with intensive Cu-3p lines. In the case of the nanocomposite, the quantification of the AgPt NPs yields a platinum content of roughly 15 at% within the nanoparticles. A detailed investigation of AgPt NPs can be found in our earlier works [7,11].

In addition to the functionalisation of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O nanocomposite with AgPt NPs, we also used Pd nanoparticles [28] to prepare the decorated sensors in the context of this work. The respective overview and high-resolution spectra corresponding to the TiO<sub>2</sub>/CuO structures with and without decoration by Pd NPs are shown in Figure S4 (Supporting Information). In general, the spectra of the AgPt nanoparticle- and Pd nanoparticle-decorated sensors show strong similarities and mostly differ in the signals corresponding to the elemental Ag, Pt or Pd. The observation of the Pd-3d lines with peaks around 335.8



*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

eV (Pd-3d<sub>5/2</sub>) and 341.0 eV (Pd-3d<sub>3/2</sub>) indicates the successful decoration of the sensor structure by Pd nanoparticles [28].

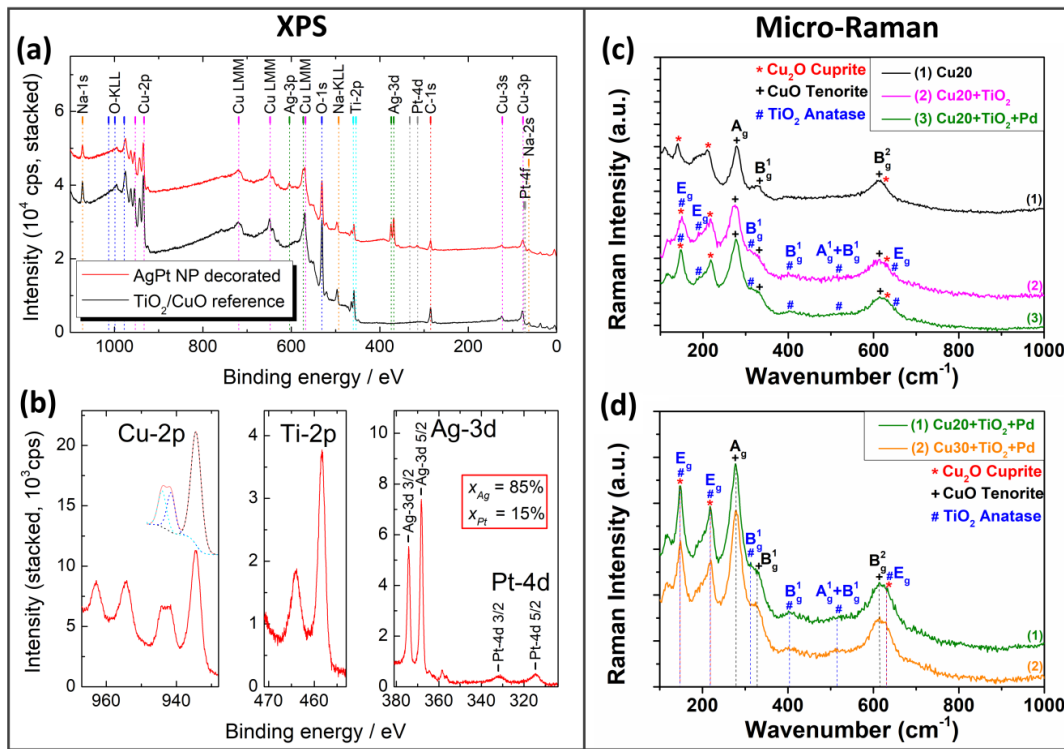


Fig. 3. X-ray photoelectron spectra (XPS) of: (a) a AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (red line) nanocomposite and an undecorated TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O thin film (black line); (b) spectra at higher resolution for Cu-2p and Ti-2p lines as well as spectra for Ag-3d and Pt-4d lines. Micro-Raman spectra for: (c) the surface functionalized TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O and Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 20 nm (Cu<sub>20</sub>) after being thermally treated at 420°C for 30 min in ambient; (d) Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O with CuO/Cu<sub>2</sub>O thicknesses of 20 nm (Cu<sub>20</sub>) and 30 nm (Cu<sub>30</sub>), respectively.

The micro-Raman spectra of the CuO/Cu<sub>2</sub>O, TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O and Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O nanocomposites, which was investigated at room temperature in the range 100-1000 cm<sup>-1</sup>, are shown in Figure 3c and Figure 3d. The presence of metallic Cu and Pd could not be ascertained in these materials, due to the instrumental limitations related to the measurement of their dielectric constants, which possess negative real and imaginary positive components exhibited in the surface plasmon resonance (SPR) experiments

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

[68,69]. In the case of the metal nanoclusters, the local SPRs are pledged for the field improvement, which undergo surface-enhanced processes [68,69], that are only observed when using surface-enhanced Raman spectroscopy. Only phonon frequencies of the crystalline Cu<sub>2</sub>O, CuO and TiO<sub>2</sub> layers are observed with our experimental set-up, as the group theory indicates that the Raman response is a function of the space group symmetry of the crystal [70].

Figure S5 illustrate the Ultraviolet, Visible and Near InfraRed (UV-Vis-NIR) absorption spectra for the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O heterostructures, which confirm the energy structures and optical properties of this transparent semiconducting oxide. The Tauc plots for the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O heterostructures, presented in Figure S6, reveal a bandgap that widens with the reduction of the nanoparticle size from 30 to 10 nm. As expected, the absorption edge of 2.04 eV for the 20 nm sample is equal to the value published for bulk Cu<sub>2</sub>O [71–74].

### **3.3 Gas sensing properties**

Heterostructures formed by *p-n* semiconductors, especially those functionalized with noble metals have a high catalytic activity and can be used to enhance the surface reactions of chemical sensing materials [7,75]. It is known that the functionalization of oxides (such as ZnO, SnO<sub>2</sub>, TiO<sub>2</sub>, Cu<sub>2</sub>O and Fe<sub>2</sub>O<sub>3</sub>) with different noble metals or their alloys improves significantly their sensing performance. In this section the sensing properties of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O heterostructure functionalized with the Pd, Ag or AgPt NPs will be discussed.

#### **3.3.1 Gas sensing properties of Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O heterostructures**

The gas sensing characteristics of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 20 nm (Cu20) functionalized using Pd NPs (Pd-NPs/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O) were investigated towards different volatile organic compounds and hydrogen. Our main aim is to show



experimentally that Pd-functionalization of such structures significantly increases the response and selectivity to hydrogen gas, even at low operating temperature. We also intend to demonstrate that it is possible to lower the energy consumption during operation and tune the reactivity toward H<sub>2</sub> of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O heterojunction sensors through functionalization by Pd nanoparticles.

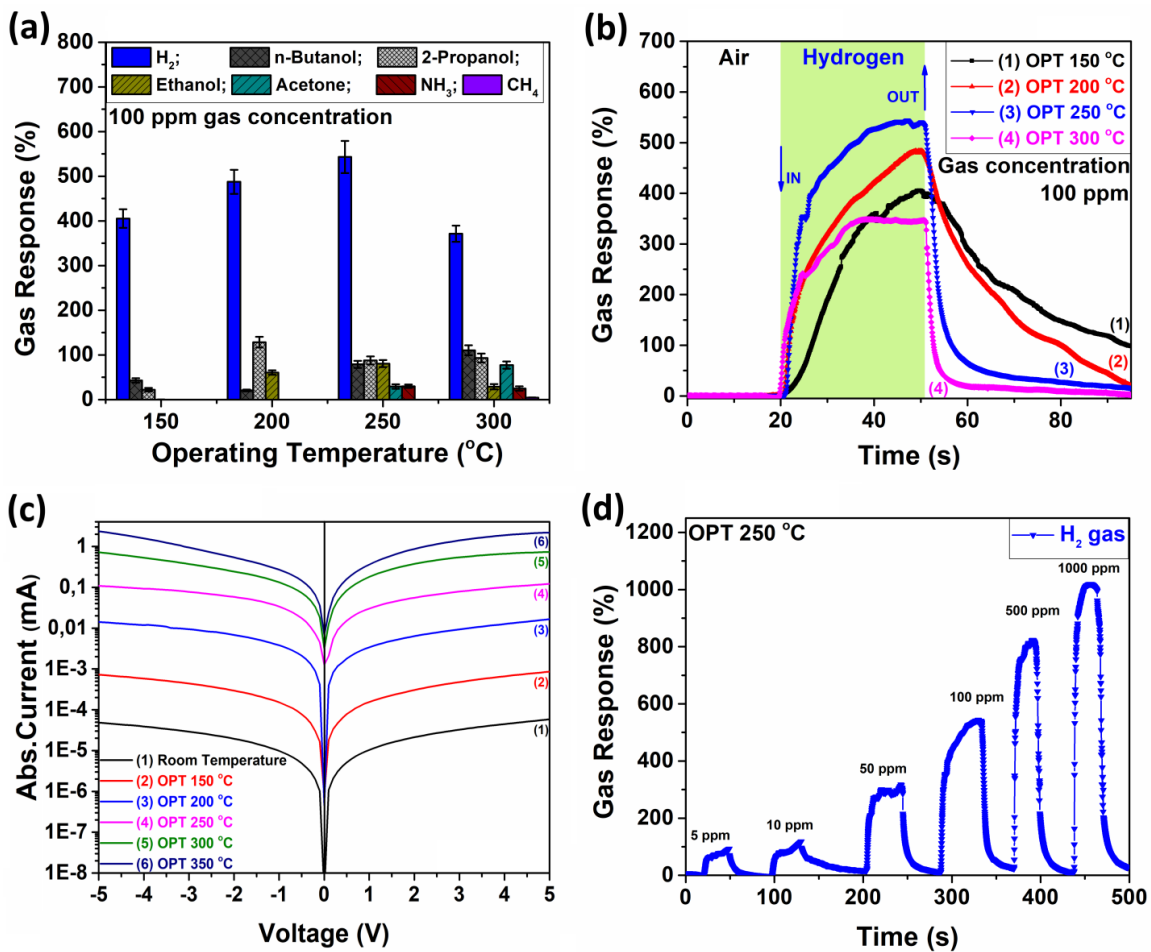


Fig. 4. (a) Gas response towards different compounds (hydrogen, *n*-butanol, 2-propanol, ethanol, acetone, ammonia and CH<sub>4</sub>) of the Pd-functionalized TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 20 nm (Cu20) at different operating temperatures (OPT); (b) Dynamic response to hydrogen of the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 20 nm (Cu20) measured at several OPTs; (c) The I-V current-voltage characteristics of the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 20 nm (Cu20) at different OPT; (d) Dynamic response to different concentrations of hydrogen (5, 10, 50, 100, 500

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

and 1000 ppm) of the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 20 nm (Cu20) (applied bias voltage of 250 mV).

Figure 4a shows the response versus operating temperature to hydrogen, *n*-butanol, 2-propanol, ethanol, acetone, ammonia and CH<sub>4</sub> by the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples after surface functionalization with the Pd-NPs (for a CuO/Cu<sub>2</sub>O specimen of 20 nm of thickness labelled as Cu20 set sample), where we observe a high and selective response to H<sub>2</sub> at all working temperatures. The responses are ~405%, ~487%, ~543% and ~371% at the operating temperatures of 150°C, 200°C, 250°C and 300°C, respectively. The optimal operating temperature was found within the range 200-250°C. Figure 4b shows the dynamic hydrogen response of the Pd-NPs/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu20) samples at different operating temperatures. The calculated response times ( $\tau_r = 18.7, 20.4, 12.8$  and  $12.4$  s) and recovery times ( $t_d = (> 50), 36.3, 10.6$  and  $4.2$  s) are relatively small at the operating temperatures of 150°C, 200°C, 250°C and 300°C, respectively, see Figure S7a. The dynamic response to different gases (hydrogen, *n*-butanol, 2-propanol, ethanol, acetone, ammonia and CH<sub>4</sub>) of Pd-NPs/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O with CuO/Cu<sub>2</sub>O thickness of 20 nm (Cu20) at an operating temperature of 250°C can be seen in Figure S7b. Figure 4c shows that the current increases with the operating temperature for the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O material. Figure 4d shows the dynamic response to different hydrogen concentrations (5, 10, 50, 100, 500 and 1000 ppm) of the functionalized Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu20) samples, where a fairly high response of ~88% is registered at 5 ppm. The dynamic response to H<sub>2</sub> gas with concentrations of 5 and 50 ppm is presented in Figure S8.

Figure S9a presents the response to hydrogen, *n*-butanol, 2-propanol, ethanol, acetone and ammonia of the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (for a substrate with CuO/Cu<sub>2</sub>O thickness of 30 nm, referred as Cu30) samples, which possess the highest response towards H<sub>2</sub> gas (> 550%). Figure S9c displays the dynamic response to hydrogen of the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu30) samples at various OPTs and Figure S9d illustrates the dynamic response to hydrogen gas with three consecutive pulses at the operating temperatures 300°C. These samples clearly

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

show superior sensing performances, which can be of major practical interest in device applications.

### 3.3.2 Gas sensing properties of Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O

The surface functionalization with the Ag nanoparticles of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples (CuO/Cu<sub>2</sub>O with thickness of 60 nm (Cu60)) were realized next to tune the response to VOCs, namely to change the selectivity from ethanol (in the case of the CuO/Cu<sub>2</sub>O samples) to *n*-butanol.

Figure 5a shows the response to several gases versus the OPTs of the surface functionalized Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples (CuO/Cu<sub>2</sub>O with thickness of 60 nm). We observe that, at the low operating temperatures of 200°C, the sample has *n*-type conductivity and shows sensing capabilities only towards 2-propanol and ethanol, because the electrical resistivity decreases after the molecular interactions. At the working temperatures OPTs of 250°C, 300°C and 350°C, the sample already has *p*-type conductivity and is therefore selective to *n*-butanol, where the responses are ~54%, ~200%, and ~163%, respectively. This phenomenon is dictated by the composition of the sample, which change the surface activity and reaction products [7,22,23] by band bending and formation of electron depletion or space charge layer in the conduction band, so the conductivity of the active materials either decreases or increases [76]. The lower operating temperature may not influence the depletion layer of electrons in TiO<sub>2</sub>, and the CuO/Cu<sub>2</sub>O layer has a higher resistance, the current flows through the TiO<sub>2</sub> layer which is an *n*-type semiconductor, but at a higher operating temperature the depletion layer of electrons in TiO<sub>2</sub> and the accumulation layer of holes in CuO/Cu<sub>2</sub>O are also influenced, thus leading to the CuO/Cu<sub>2</sub>O layer predominating in the sensing mechanism leading to the increase of the heterojunction resistance to the application of the target gas [77]. Figure 5b shows the dynamic response towards hydrogen, *n*-butanol, 2-propanol, ethanol and acetone for the Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples at the optimal OPT of 300°C.

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

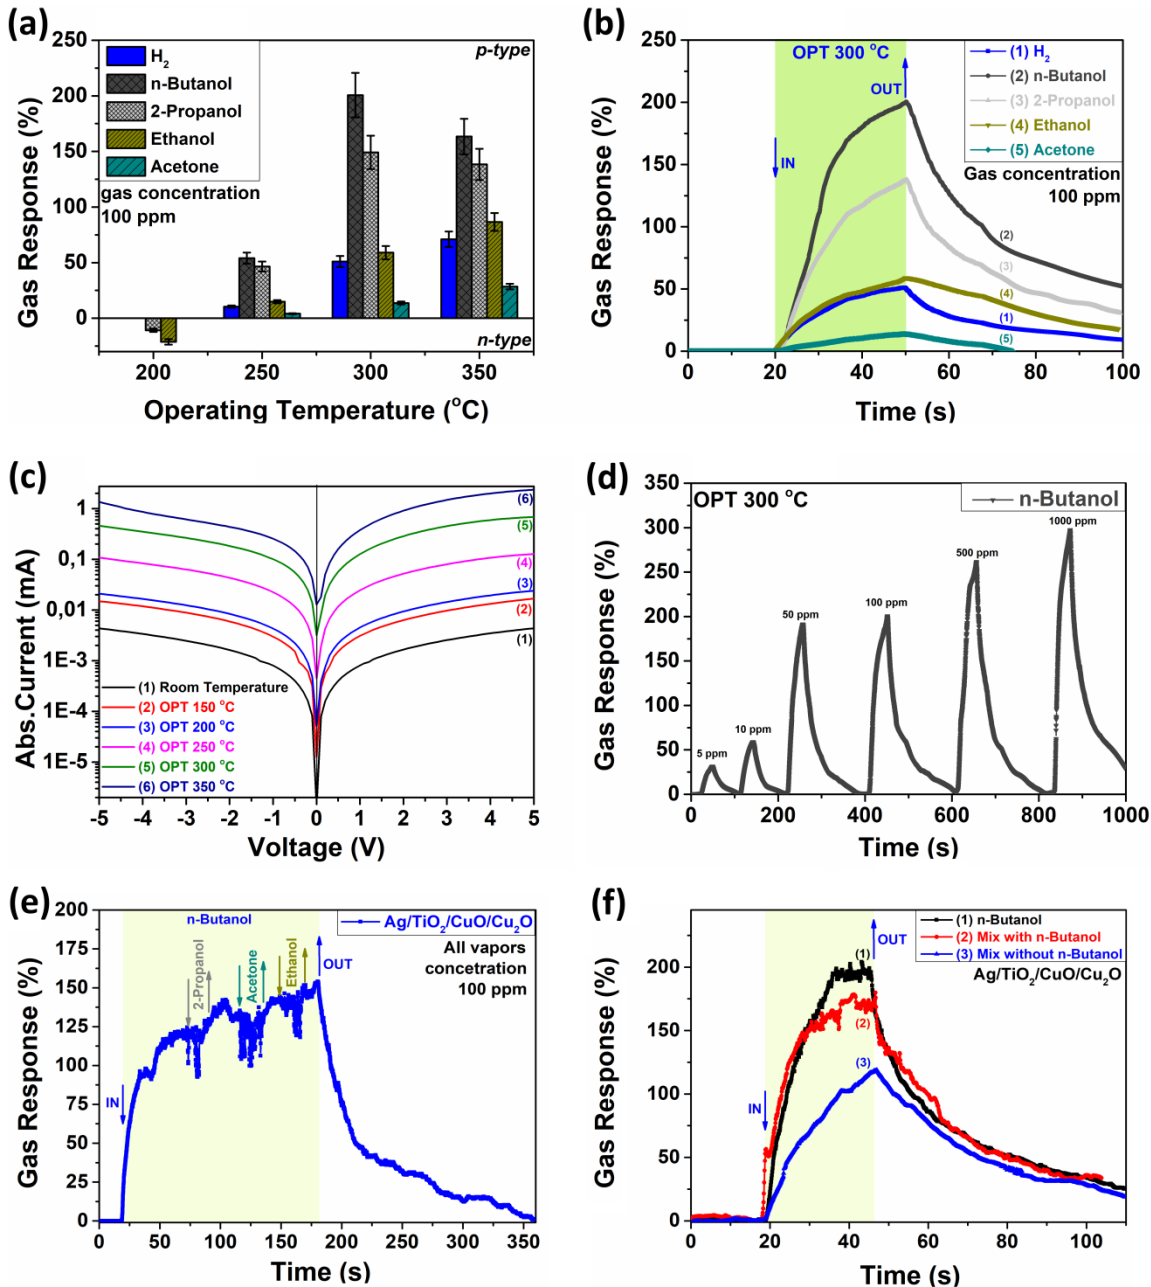


Fig. 5. (a) Gas response towards hydrogen, *n*-butanol, 2-propanol, ethanol and acetone for the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples after surface functionalization with Ag-nanoparticles (CuO/Cu<sub>2</sub>O with thickness of 60 nm (Cu60)); (b) Dynamic response to different compounds (hydrogen, *n*-butanol, 2-propanol, ethanol and acetone) of the Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples at the operating temperature of 300°C. (c) The current –

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

voltage behavior of the Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples at different operating temperatures; (d) Dynamic response to various concentrations of *n*-butanol (5, 10, 50, 100, 500 and 1000 ppm) of the Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples (applied bias voltage 27.5 mV). (e) Dynamic response to 100 ppm of *n*-butanol and consecutively 2-propanol, acetone, ethanol in air of Ag/ TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples. (f) Dynamic response to 100 ppm of *n*-butanol and mixture of alcohols in air, with and without *n*-butanol vapors with 1000 ppm of Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples.

Figure 5c shows the current-voltage performance of the Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples, where the conductance increases with the operating temperature in the tested range. Figure 5d displays the dynamic response to 5, 10, 50, 100, 500 and 1000 ppm of *n*-butanol for the Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples, demonstrating that a response of about 31% is registered even for the lowest concentration of this gas. The dynamic response to 5, 50 and 100 ppm of *n*-butanol of the Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 60 nm (Cu60) at the operating temperature of 300°C is presented in Figure S10. Figure 5e displays the dynamic response to 100 ppm of *n*-butanol and consecutively 2-propanol, acetone, ethanol in air, of Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples. Figure 5f displays the dynamic response to 100 ppm of *n*-butanol and mixtures of alcohols in air, with and without *n*-butanol vapors, with 1000 ppm of Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples.

### **3.3.3 Gas sensing properties of AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O**

Next, the response to different compounds by the AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples were studied at various working temperatures to investigate whether we can tune the selectivity by means of changing the composition of the NPs.

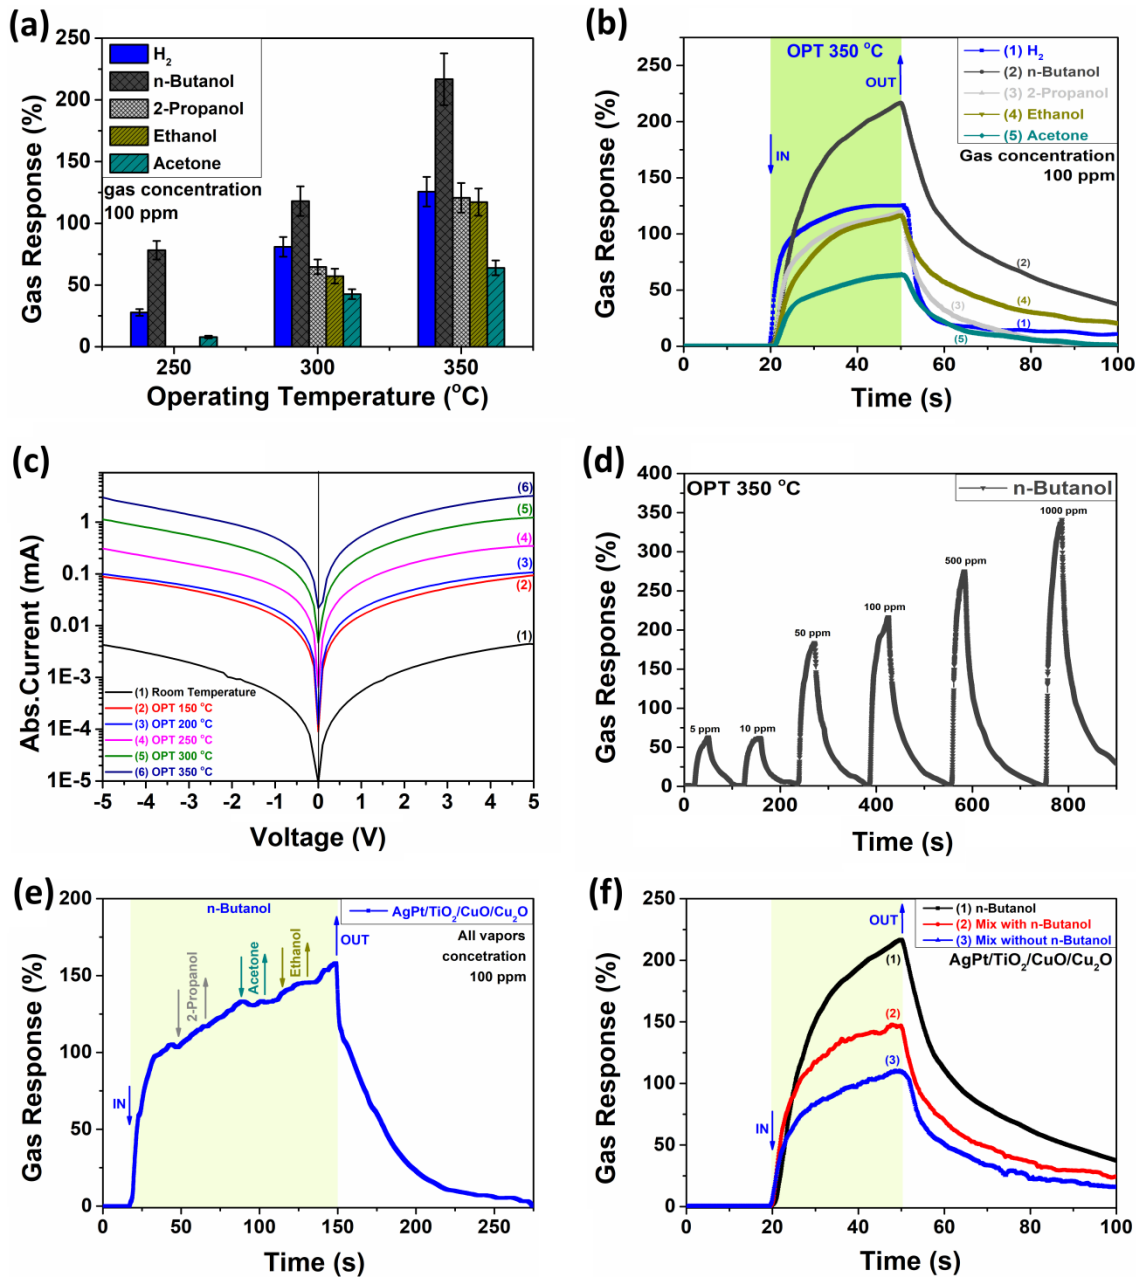


Fig. 6. (a) Gas response to different gases and volatiles (hydrogen, *n*-butanol, 2-propanol, ethanol and acetone) of the AgPt-NPs surface functionalized TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 60 nm (Cu60); (b) Dynamic response to hydrogen, *n*-butanol, 2-propanol, ethanol and acetone for AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples at the operating temperature of 350°C. (c) Current-voltage characteristic of the AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples at different operating temperatures; (d) Dynamic response to 5, 10, 50, 100, 500 and 1000 ppm of *n*-butanol of AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples (applied bias voltage 9.5 mV). (e) Dynamic response to 100 ppm of *n*-butanol and consecutively 2-propanol, acetone,



*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

ethanol in air of AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples. (f) Dynamic response to 100 ppm of *n*-butanol and mixtures of alcohols in air with and without *n*-butanol vapors with 1000 ppm of AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples.

Figure 6a shows the response to hydrogen, *n*-butanol, 2-propanol, ethanol and acetone versus the OPT for the surface-functionalized AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 60 nm (Cu60). At the OPT of 250°C, 300°C and 350°C, the sample is selective to *n*-butanol and the responses are ~78%, ~118%, and ~216%, respectively, suggesting that the optimal operating temperature is therefore 350°C. Figure 6b illustrate the dynamic response to hydrogen, *n*-butanol, 2-propanol, ethanol and acetone of the AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples at the operating temperatures of 350°C. Figure 6c illustrate the current-voltage characteristics of AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (Cu60) samples, where we observe that the conductance increases with the operating temperature. Figure 6d shows the dynamic response to 5, 10, 50, 100, 500 and 1000 ppm of *n*-butanol for the Cu60 AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 60 nm, where a response of ~63% is registered for 5 ppm of *n*-butanol. Figure 6e displays the dynamic response to 100 ppm of *n*-butanol and consecutively 2-propanol, acetone, ethanol in air of AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples. Figure 6f displays the dynamic response to 100 ppm of *n*-butanol and mixtures of alcohols in air with and without *n*-butanol vapors with 100 ppm of AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples. The dynamic response of the AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples (Cu60) to 5, 50 and 100 ppm of *n*-butanol at the OPT of 350°C is presented in Figure S11. Thus, chemical sensitization facilitates the adsorption of certain gas molecules on the metal NP surface, thus inducing more interactions with pre-absorbed oxygen species, facilitating relevant chemical reactions and therefore an improved gas detection performance [5,6].

### **3.3.4 Comparison of the gas sensing properties and energy consumption of the heterostructures**

In this section, we compare the gas responses for the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O heterostructures functionalized with the different types of NPs-, as we aim to show the possibility of controlling their selectivity by using the technological approach developed in this work.

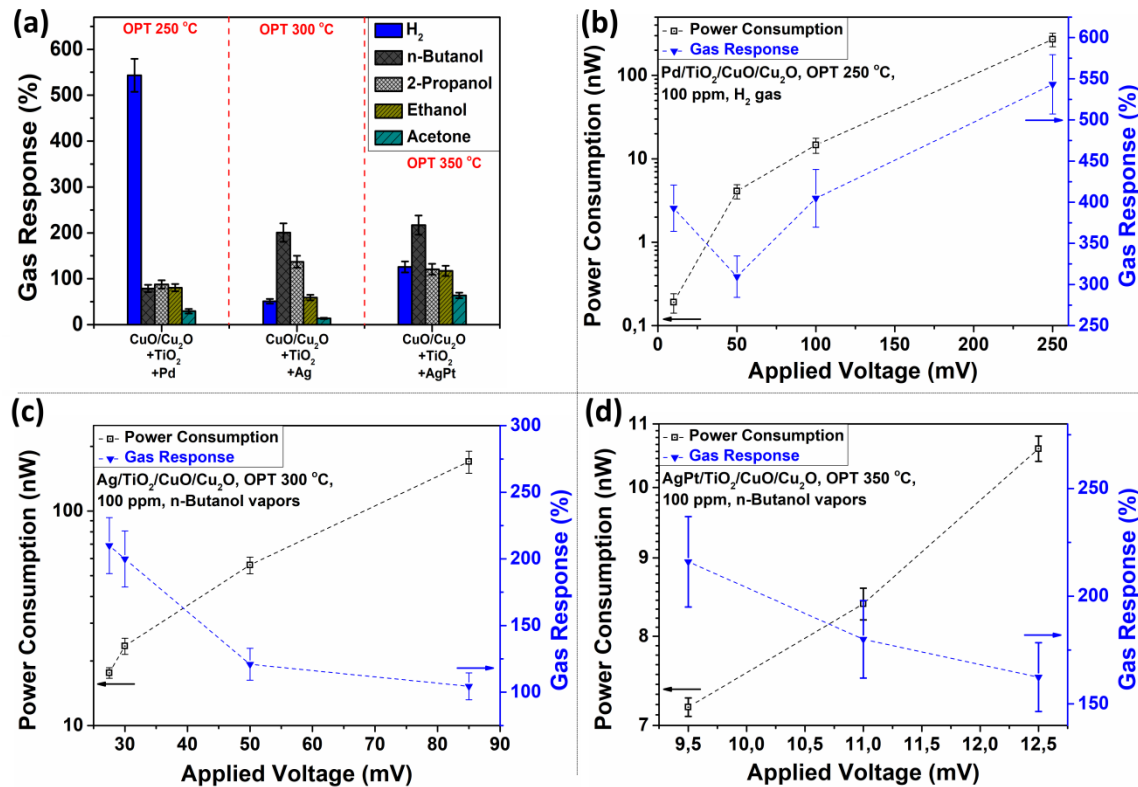


Fig. 7. (a) Gas response to different compounds (hydrogen, *n*-butanol, 2-propanol, ethanol and acetone) of the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O, Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O, and AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples. Dependence of the power consumption and of the gas versus the applied bias voltage for: (b) Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (with CuO/Cu<sub>2</sub>O thickness of Cu20), (c) Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (with CuO/Cu<sub>2</sub>O thickness of Cu60), and (d) AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O (with CuO/Cu<sub>2</sub>O thickness of Cu60).

Figure 7a shows the gas response to hydrogen, *n*-butanol, 2-propanol, ethanol and acetone for the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O, Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O, and AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples. The samples functionalized with Pd nanoparticles are the most sensitive to hydrogen, whereas the samples functionalized using the Ag and AgPt nanoparticles experience a change of selectivity and are the most sensitive to butanol.



Figure 7b represents the dependence of the power consumption and of the response to 100 ppm of H<sub>2</sub> gas versus the applied bias voltage for the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 20 nm (Cu20). According to the figure, both the power consumption and the response to the H<sub>2</sub> gas decreases when the applied voltage is decreased. However, we also observed that for an applied bias voltage of 10 mV the response increased. The power consumption obtained is ~270, ~140, ~4.1 and ~0.19 nW, and the responses are ~588%, ~404%, ~310% and ~390%, at the applied bias voltages of 250, 100, 50 and 10 mV, respectively. The response to different gases versus the applied bias voltage for the Pd/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 20 nm (Cu20) is represented in Figure S12. The dependence on the power consumption and the response to 100 ppm of *n*-butanol vapors versus applied bias voltage for Ag/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O with CuO/Cu<sub>2</sub>O thickness of 60 nm are represented in Figure 7c, where it can be seen that the obtained power consumption is ~170, ~56, ~23.5 and ~17.6 nW, and the respective responses are ~104%, ~121%, ~200% and ~210%, at the applied bias voltages of 85, 50, 30 and 27.5 mV, respectively. For the AgPt/TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 60 nm (Cu60), the power consumption is ~10.6, ~8.4 and ~7.2 nW, and the responses are ~162%, ~180% and ~216% to 100 ppm of *n*-butanol vapors at the applied bias voltages of 12.5, 11.0 and 9.5 mV, respectively, shown in Figure 7d, where it can be seen that the obtained power consumption is ~10.6 nW, ~8.4 nW and ~7.2 nW, and the respective responses are ~162%, ~180% and ~216%, at the applied voltages of 12.5 mV, 11.0 mV and 9.5 mV, respectively. The dependence on the power consumption versus the applied bias voltage is represented in Figure S13 for the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O samples with CuO/Cu<sub>2</sub>O thickness of 20 nm (Cu20) decorated with Pd or Ag or AgPt NPs.

The proposed gas sensing mechanism for our heterostructures after functionalization with noble metal nanoparticles is described in Text S1 (Supporting Information).

### 3.4 Deposition of nanoparticles: computational results

We have simulated the modification of the ternary  $\text{TiO}_2(111)/\text{CuO}(\bar{1}\bar{1}\bar{1})/\text{Cu}_2\text{O}(111)$  heterostructure by adsorbing  $\text{Pd}_7$ ,  $\text{Ag}_7$  and  $\text{Ag}_6\text{Pt}$  nanoparticles, see Figure 8, to subsequently assess their selectivity and sensitivity towards the detection of hydrogen ( $\text{H}_2$ ), ethanol ( $\text{C}_2\text{H}_5\text{OH}$ ) and *n*-butanol ( $\text{C}_4\text{H}_9\text{OH}$ ) vapors. The purpose of these simulations is to assist the interpretation of the trends of the gas response detected in experiments for our ternary heterojunctions functionalised using noble metal nanoparticles.

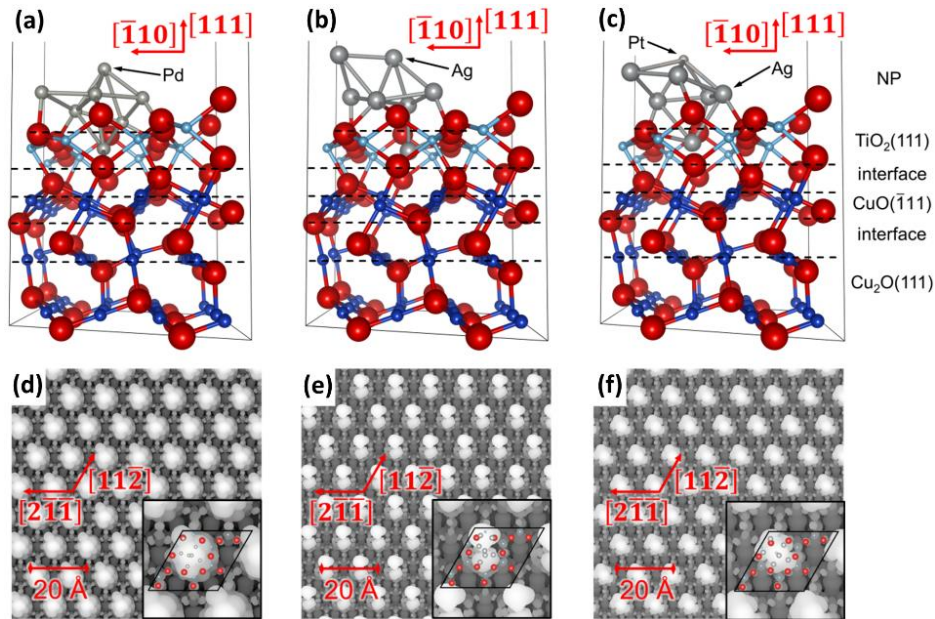


Fig. 8. (Top panels) Side view and (bottom panels) simulated scanning tunnelling microscopy (STM) images of the ternary  $\text{TiO}_2(111)/\text{CuO}(\bar{1}\bar{1}\bar{1})/\text{Cu}_2\text{O}(111)$  heteroepitaxial junction functionalised using (a and d)  $\text{Pd}_7$ ; (b and e)  $\text{Ag}_7$ ; and (c and f)  $\text{Ag}_6\text{Pt}$  nanoparticles. The ternary heterojunctions functionalised using the  $\text{Pd}_7$ ,  $\text{Ag}_7$  or  $\text{Ag}_6\text{Pt}$  nanoparticle are displayed using the ball-and-stick representation. The STM images were generated using a bias of: (d)  $V = -0.5$  eV, (e)  $V = -1.0$  eV and (f)  $V = -1.5$  eV, an electron density of (d)  $\rho = 0.0009 \text{ e } \text{\AA}^{-3}$ , (e)  $\rho = 0.0029 \text{ e } \text{\AA}^{-3}$  and (f)  $\rho = 0.0070 \text{ e } \text{\AA}^{-3}$  as well as a tip distance of (d)  $d = 2.25 \text{ \AA}$ , (e)  $d = 1.06 \text{ \AA}$  and (f)  $d = 2.17 \text{ \AA}$ . Inset illustrate enlargement of the STM image for the surface unit cell. Crystallographic directions are indicated with respect to the  $\text{Cu}_2\text{O}(111)$  substrate. O atoms are in red, Cu atoms are in dark blue, Ti atoms are in light blue and Pd, Ag or Pt atoms are in grey.

The scanning tunnelling microscopy images (STM), shown in Figure 8d-f, were simulated using the HIVE code [78], which is based on the theory developed by Tersoff and Hamann

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

[79]. The brightest spots resolved for the surface of the nanoparticle-functionalised ternary TiO<sub>2</sub>(111)/CuO( $\bar{1}11$ )/Cu<sub>2</sub>O(111) material correspond to the noble metal clusters. Figure 8d clearly shows the almost perfect 5-fold symmetry of the Pd<sub>7</sub> NP, which is only broken by the Pd atom located away from the nanoparticle axis. Following deposition, the Ag<sub>7</sub> cluster splits into conjoined twin particles, each containing three metal atoms, connected by a bridge comprising one Ag atom, as shown in Figure 8e. Figure 8f illustrates that replacing the axial and exposed Ag atom by Pt has a cohesive effect in the conjoined twin particles, which reattach in a pentagon shape, although still more distorted than Pd<sub>7</sub>. We discuss changes in the interfacial energy and work function after NP functionalisation of TiO<sub>2</sub>(111)/CuO( $\bar{1}11$ )/Cu<sub>2</sub>O(111) in the SI. The adsorption energies of the noble metal NPs, charge transfers and their magnetic moments are also analysed in the Text S2 (Supporting Information).

The work function of the ternary heterojunction suffers a reduction of approximately 37% from its initial large value of  $\Phi = 7.454$  eV, after decoration by the noble metal nanoparticles, as listed in Table S1 and described in the Text S3 (Supporting Information). The lower work function values calculated for the hetero-devices after surface functionalisation explain their enhanced chemical reactivity, compared to the material before deposition of the metal nanoclusters. Our simulated work functions show small differences of up to 0.14 eV, suggesting that the composition of the nanoparticles can be used to fine-tune the application of the nano-composite materials as chemical sensors.

### 3.5 Adsorption of molecules: computational results

Here, we have modelled the surface chemistry of the ternary heteroepitaxial junction materials decorated with the nanoparticles of noble metals or their alloys.

The binding energies for the interaction between the adsorbate molecules and the TiO<sub>2</sub>(111)/CuO ( $\bar{1}11$ ) /Cu<sub>2</sub>O(111) layered material functionalised with the Pd<sub>7</sub> nanoparticle, show a preference for H<sub>2</sub>, releasing  $-1.494$  eV upon interaction, see Table

S2. Table S2 also lists the adsorption energies ( $E_{\text{ads}}$ ) for Ag<sub>7</sub>/TiO<sub>2</sub>(111)/CuO ( $\bar{1}11$ )/Cu<sub>2</sub>O(111) and Ag<sub>6</sub>Pt/TiO<sub>2</sub>(111)/CuO ( $\bar{1}11$ )/Cu<sub>2</sub>O(111), which display a strong shift of preference towards *n*-C<sub>4</sub>H<sub>9</sub>OH, with calculated  $E_{\text{ads}} = -1.129$  eV and  $-1.053$  eV, respectively, on the equatorial site of the NPs. However, the adsorption of the largest molecular weight alcohol on the least coordinated axial site of the NPs leads to a reduced binding energy by around 50% compared to its equatorial Ag counterpart position. Our calculations reveal that the decreasing order of strength of molecular adsorption is  $E_{\text{ads}}(n\text{-C}_4\text{H}_9\text{OH}) > E_{\text{ads}}(\text{C}_2\text{H}_5\text{OH}) > E_{\text{ads}}(\text{H}_2)$  after replacing the axial Ag atom by Pt in Ag<sub>7</sub>, as shown in Table S2.

Figure 9a-c displays the thermodynamically most stable adsorption geometries for the interaction of the three molecules investigated computationally on the exposed facet of the heterostructure containing the noble metal clusters. We found that the diatomic H<sub>2</sub> molecule dissociates upon adsorption onto the equatorial Pd atoms of the nanoparticle, leading to the strongest interaction found in this work, see Figure 9a. For this binding mode, our calculations suggest that the H atoms place themselves approximately along the  $[\bar{2}11]$  direction at either sides of the axial Pd atom. Thus, each H adatom forms a binuclear complex by coordinating both one equatorial and the axial Pd atom at the average distances of 1.71 Å and 1.78 Å. Figure S15a-c shows the binding configurations of H<sub>2</sub>, C<sub>2</sub>H<sub>5</sub>OH and *n*-C<sub>4</sub>H<sub>9</sub>OH on the most favourable adsorption sites of the Pd<sub>7</sub>/TiO<sub>2</sub>(111)/CuO( $\bar{1}11$ )/Cu<sub>2</sub>O(111) sensor. For the heterostructure containing the Pd<sub>7</sub> clusters, H<sub>2</sub> interacts molecularly and nearly vertically at 1.75 Å above the 5-fold axial Pd site (see Figure S15a), where it shows the least favourable adsorption observed on this material. C<sub>2</sub>H<sub>5</sub>OH moved outwards during the geometry optimisation from the initial equatorial site, forming a laterally coordinate bond of 2.27 Å to the axial Pd atom in its most stable adsorption configuration, as shown in Figure S15b. The O atom from the largest molecular weight alcohol stays above the initial adsorption site, *i.e.* at 2.23 and 2.13 Å from

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

the axial and equatorial Pd sites, see Figure S14c. The Bader partition scheme reveals that H<sub>2</sub> lost electronic density upon adsorption, as shown in Table S2.

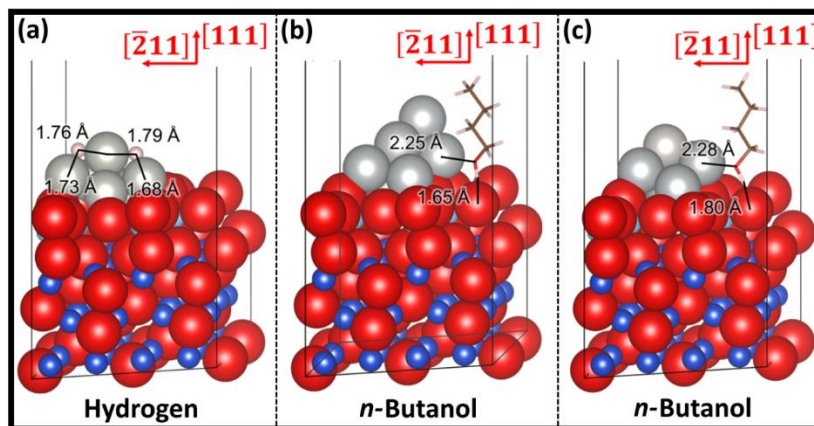


Fig. 9. Adsorption of: (a) H<sub>2</sub>, and (b and c) *n*-C<sub>4</sub>H<sub>9</sub>OH on the TiO<sub>2</sub>(111)/CuO( $\bar{1}\bar{1}\bar{1}$ )/Cu<sub>2</sub>O(111) heterostructure decorated with the Pd<sub>7</sub>, Ag<sub>7</sub> and Ag<sub>6</sub>Pt clusters, respectively. Interatomic distances are shown and crystallographic directions are indicated with respect to the Cu<sub>2</sub>O(111) substrate. The ternary heterojunctions functionalised using the Pd<sub>7</sub>, Ag<sub>7</sub> or Ag<sub>6</sub>Pt nanoparticles are displayed using the space-filling representation, whereas the adsorbates are shown using the stick representation. O atoms are in red, H atoms are in white, C atoms are in brown, Cu atoms are in dark blue, Ti atoms are in light blue and Pd, Ag and Pt atoms are in grey.

Figure S15d-f illustrates the binding configurations of H<sub>2</sub>, C<sub>2</sub>H<sub>5</sub>OH and *n*-C<sub>4</sub>H<sub>9</sub>OH on the most favourable adsorption sites of the Ag<sub>7</sub>/TiO<sub>2</sub>(111)/CuO( $\bar{1}\bar{1}\bar{1}$ )/Cu<sub>2</sub>O(111) sensor. The H<sub>2</sub> molecule adsorbs molecularly at approximately 2.0 Å above the axial and to the side of the equatorial sites of the Ag<sub>7</sub> nanocluster, see Figure S15d. The sensor can only exert a minor effect on the intramolecular H–H distance, with respect to the isolated H<sub>2</sub> molecule, which was calculated at 0.79 Å in both types of adsorption positions. We found that the C<sub>2</sub>H<sub>5</sub>OH molecule forms a vertical coordinate bond on the axial site with an O–Ag distance of 2.35 Å, which becomes 0.03 Å shorter on the equatorial adsorption position, as shown in Figure S15e. Interestingly, *n*-C<sub>4</sub>H<sub>9</sub>OH moves laterally towards a surface O to form a hydrogen bond of 1.65 Å, resulting in the shortest O–Ag distance of 2.25 Å, which explains the largest binding energy calculated for this system in the equatorial site, see Figure 9b.



*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

However, the largest molecular weight alcohol, *n*-butanol, interacts perpendicularly with the axial Ag atom at the slightly elongated distance of 2.31 Å. We observed that C<sub>2</sub>H<sub>5</sub>OH (*n*-C<sub>4</sub>H<sub>9</sub>OH) forms a vertical adsorption configuration on the heterostructure decorated using the Ag<sub>7</sub> nanoparticles.

For the molecular adsorptions on the sensor decorated by the Ag<sub>7</sub> nanoparticles, the Bader charge transfers were calculated between −0.039 and −0.074 e<sup>−</sup>, see Table S2. These values indicate that the adsorbate loses electronic density to the heterojunction functionalised with the nanocluster, showing no clear correlation with the binding energies of the VOC and H<sub>2</sub> molecules. The small values of electron density flow that we have calculated for this material support the low sensitivity that it displayed in the experiments.

Figure S15g-i depicts the structures of the molecular interactions with the surface sites of the heteroepitaxial material decorated with Ag<sub>6</sub>Pt that released the largest adsorption energies. We found that H<sub>2</sub> remained perpendicularly atop the axial Pt atom at 1.91 Å, while it coordinated laterally the equatorial Ag site at the more elongated distance of 2.07 Å, which moved outwards upon adsorption, see Figure S15g. Our DFT modelling suggests that C<sub>2</sub>H<sub>5</sub>OH prefers to stay parallel to the surface, binding both adsorption sites at the same distance of 2.29 Å, regardless of the different chemical nature of the metal atom, as shown in Figure S15h. When *n*-C<sub>4</sub>H<sub>9</sub>OH interacts with the axial or equatorial adsorption sites, the large alkyl radical positions itself perpendicularly to the surface. Figure 9c illustrates that *n*-C<sub>4</sub>H<sub>9</sub>OH has a bidentate coordination mode with Ag<sub>6</sub>Pt/TiO<sub>2</sub>(111)/CuO( $\bar{1}\bar{1}\bar{1}$ )/Cu<sub>2</sub>O(111), by binding laterally to the equatorial Ag atom and by forming a hydrogen bond between the hydroxyl H and one of the surface O species. Moving this alcohol to the axial site forces a reduction of the interfacial O–Pt distance to 2.23 Å, which is nevertheless insufficient to counteract the loss of the hydrogen bond formed on the equatorial Ag site.

Our calculated charge transfers indicate that most of the adsorbates donate electron density to the sensor containing the Ag<sub>6</sub>Pt nanoclusters, see Table S2. The electronic charges transferred by C<sub>2</sub>H<sub>5</sub>OH to the axial and equatorial sites of the nanoparticle are −0.085 and

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

$-0.098\text{ e}^-$ , respectively, displaying a direct correlation with the adsorption energies released in these positions. In contrast, *n*-C<sub>4</sub>H<sub>9</sub>OH donated  $-0.065\text{ e}^-$  in the most stable adsorption configuration on Ag<sub>6</sub>Pt, a value that nearly doubled in the axial Pt position, leading to the largest charge transfer on this sensor. Despite H<sub>2</sub> having very close binding energies on both adsorption sites of Ag<sub>6</sub>Pt, our models suggest that those interactions cause opposite flows of electron density, with the molecule receiving a charge of  $0.011\text{ e}^-$  in the axial position. To verify that the system is in a stable condition in Figure S16 are provided corresponding DOS.

A discussion of the adsorption geometries and charge transfers for the least favourable interactions can be found in the Text S4 (Supporting Information).

#### **4. Summary and Outlook**

Changing the composition of the nanolayered CuO/Cu<sub>2</sub>O structure with a total thickness of 60 nm by first depositing 20 nm of TiO<sub>2</sub> on top and subsequently Ag nanoparticles (5-15 nm of diameter), reduces of the energy consumption of the final gas sensing device to below 1 nW. This fabrication process also allows tuning the response spectrum of the sensor, thereby promoting the selectivity to 100 ppm of *n*-butanol vapours (response of over 200% at the operating temperature of 300°C). In the case of AgPt functionalization, the response of the sensor increases even higher to 220% for 100 ppm of *n*-butanol vapours at an operating temperature of 350°C. In the case of Pd functionalization the selectivity of the sensor was changed from ethanol to hydrogen H<sub>2</sub>, and the sensing performance was enhanced compared to the other compounds (response in the range between 400-600% at the lower operating temperature of 150-250°C).

A tentative surface reaction mechanism explaining the sensing behavior is proposed. At the interface of the TiO<sub>2</sub>/CuO/Cu<sub>2</sub>O heterostructure, the ethanol molecule first suffers a reduction and then is combined with the holes present in CuO, producing the CH<sub>3</sub>CHO intermediate, which finally reacts with the oxygen adsorbed on the *n*-type TiO<sub>2</sub> overlayer.

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

We have used thermodynamic arguments derived from DFT calculations to rationalize the stability of the heteroepitaxial material before and after surface functionalization by noble metal nanoparticles. The adsorption energies agree and support the gas sensing experiments. This manuscript presents the methodology for the nano-structuring and functionalizing of semiconducting oxides with tunable performances, as an alternative to clean room technology and micro-fabrication.

## **5. Acknowledgements**

This research was sponsored in part by the NATO Science for Peace and Security Programme (SPS) under grant G5634 „Advanced Electro-Optical Chemical Sensors” AMOXES. Dr. Lupan gratefully acknowledges PSL University, Chimie-ParisTech for invited professor positions in 2018 and 2019, CNRS Council for support as expert scientist at IRCP Chimie ParisTech, Paris. This research was sponsored partially by the German Research Foundation (DFG- Deutsche Forschungsgemeinschaft) under the schemes PAK 902 (SFB1261, FOR2093 & AD 183/16-1). This work was financially supported by the German Research Foundation (DFG) via the research unit FOR 2093 "Memristive devices for neuronal systems" through project A2. The authors would like to thank Dr. Oleksandr Polonskyi for the technical assistance and for fruitful discussion. This work has used the ARCHER UK National Supercomputing Service (<http://www.archer.ac.uk>) provided via our membership of the UK's HEC Materials Chemistry Consortium, funded by the Engineering and Physical Sciences Research Council (EPSRC grant EP/R029431). Work was also undertaken on ARC4, part of the High-Performance Computing facilities at the University of Leeds, United Kingdom. All data created during this research is provided in full in the results section of this paper.



Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. *NanoEnergy*, 88 (2021) 106241

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

## References

- [1] F. Rasch, V. Postica, F. Schütt, Y.K. Mishra, A.S. Nia, M.R. Lohe, X. Feng, R. Adelung, O. Lupan, Highly selective and ultra-low power consumption metal oxide based hydrogen gas sensor employing graphene oxide as molecular sieve, *Sensors Actuators B Chem.* 320 (2020) 128363. <https://doi.org/10.1016/j.snb.2020.128363>.
- [2] F. Xue, L. Yang, M. Chen, J. Chen, X. Yang, L. Wang, L. Chen, C. Pan, Z.L. Wang, Enhanced photoresponsivity of the MoS<sub>2</sub>-GaN heterojunction diode via the piezophototronic effect, *NPG Asia Mater.* 9 (2017) e418–e418. <https://doi.org/10.1038/am.2017.142>.
- [3] D. Zappa, V. Galstyan, N. Kaur, H.M.M. Munasinghe Arachchige, O. Sisman, E. Comini, “Metal oxide -based heterostructures for gas sensors”- A review, *Anal. Chim. Acta.* 1039 (2018) 1–23. <https://doi.org/10.1016/j.aca.2018.09.020>.
- [4] M. Hoppe, N. Ababii, V. Postica, O. Lupan, O. Polonskyi, F. Schütt, S. Kaps, L.F. Sukhodub, V. Sontea, T. Strunskus, F. Faupel, R. Adelung, (CuO-Cu<sub>2</sub>O)/ZnO:Al heterojunctions for volatile organic compound detection, *Sensors Actuators B Chem.* 255 (2018) 1362–1375. <https://doi.org/10.1016/j.snb.2017.08.135>.
- [5] S.M. Majhi, A. Mirzaei, H.W. Kim, S.S. Kim, T.W. Kim, Recent advances in energy-saving chemiresistive gas sensors: A review, *Nano Energy.* 79 (2021) 105369. <https://doi.org/10.1016/j.nanoen.2020.105369>.
- [6] J.-H. Kim, P. Wu, H.W. Kim, S.S. Kim, Highly Selective Sensing of CO, C<sub>6</sub>H<sub>6</sub>, and C<sub>7</sub>H<sub>8</sub> Gases by Catalytic Functionalization with Metal Nanoparticles, *ACS Appl. Mater. Interfaces.* 8 (2016) 7173–7183. <https://doi.org/10.1021/acsami.6b01116>.
- [7] N. Ababii, M. Hoppe, S. Shree, A. Vahl, M. Ulfa, T. Pauporté, B. Viana, V. Cretu, N. Magariu, V. Postica, V. Sontea, M.-I. Terasa, O. Polonskyi, F. Faupel, R. Adelung, O. Lupan, Effect of noble metal functionalization and film thickness on sensing properties of sprayed TiO<sub>2</sub> ultra-thin films, *Sensors Actuators A Phys.* 293 (2019) 242–258. <https://doi.org/10.1016/j.sna.2019.04.017>.
- [8] A. Vahl, J. Dittmann, J. Jetter, S. Veziroglu, S. Shree, N. Ababii, O. Lupan, O.C.

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

- Aktas, T. Strunskus, E. Quandt, R. Adelung, S.K. Sharma, F. Faupel, The impact of O<sub>2</sub>/Ar ratio on morphology and functional properties in reactive sputtering of metal oxide thin films, *Nanotechnology*. 30 (2019) 235603. <https://doi.org/10.1088/1361-6528/ab0837>.
- [9] V. Postica, A. Vahl, D. Santos-Carballal, T. Dankwort, L. Kienle, M. Hoppe, A. Cadi-Essadek, N.H. de Leeuw, M.-I. Terasa, R. Adelung, F. Faupel, O. Lupan, Tuning ZnO Sensors Reactivity toward Volatile Organic Compounds via Ag Doping and Nanoparticle Functionalization, *ACS Appl. Mater. Interfaces*. 11 (2019) 31452–31466. <https://doi.org/10.1021/acsami.9b07275>.
- [10] G. Niu, C. Zhao, H. Gong, Z. Yang, X. Leng, F. Wang, NiO nanoparticle-decorated SnO<sub>2</sub> nanosheets for ethanol sensing with enhanced moisture resistance, *Microsystems Nanoeng.* 5 (2019) 21. <https://doi.org/10.1038/s41378-019-0060-7>.
- [11] A. Vahl, O. Lupan, D. Santos-Carballal, V. Postica, S. Hansen, H. Cavers, N. Wolff, M.-I. Terasa, M. Hoppe, A. Cadi-Essadek, T. Dankwort, L. Kienle, N.H. de Leeuw, R. Adelung, F. Faupel, Surface functionalization of ZnO:Ag columnar thin films with AgAu and AgPt bimetallic alloy nanoparticles as an efficient pathway for highly sensitive gas discrimination and early hazard detection in batteries, *J. Mater. Chem. A*. 8 (2020) 16246–16264. <https://doi.org/10.1039/D0TA03224G>.
- [12] H. Liu, W. Shen, X. Chen, A room temperature operated ammonia gas sensor based on Ag-decorated TiO<sub>2</sub> quantum dot clusters, *RSC Adv.* 9 (2019) 24519–24526. <https://doi.org/10.1039/C9RA05439A>.
- [13] D. Zhao, M. Dai, Y. Zhao, H. Liu, Y. Liu, X. Wu, Improving electrocatalytic activities of FeCo<sub>2</sub>O<sub>4</sub>@FeCo<sub>2</sub>S<sub>4</sub>@PPy electrodes by surface/interface regulation, *Nano Energy*. 72 (2020) 104715. <https://doi.org/10.1016/j.nanoen.2020.104715>.
- [14] D. Zhao, H. Liu, X. Wu, Bi-interface induced multi-active MCo<sub>2</sub>O<sub>4</sub>@MCo<sub>2</sub>S<sub>4</sub>@PPy (M=Ni, Zn) sandwich structure for energy storage and electrocatalysis, *Nano Energy*. 57 (2019) 363–370. <https://doi.org/10.1016/j.nanoen.2018.12.066>.
- [15] D. Zhao, M. Dai, H. Liu, K. Chen, X. Zhu, D. Xue, X. Wu, J. Liu, Sulfur-Induced

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

- Interface Engineering of Hybrid NiCo<sub>2</sub>O<sub>4</sub>@NiMo<sub>2</sub>S<sub>4</sub> Structure for Overall Water Splitting and Flexible Hybrid Energy Storage, *Adv. Mater. Interfaces.* 6 (2019) 1901308. <https://doi.org/10.1002/admi.201901308>.
- [16] H. Liu, D. Zhao, Y. Liu, P. Hu, X. Wu, H. Xia, Boosting energy storage and electrocatalytic performances by synergizing CoMoO<sub>4</sub>@MoZn<sub>22</sub> core-shell structures, *Chem. Eng. J.* 373 (2019) 485–492. <https://doi.org/10.1016/j.cej.2019.05.066>.
- [17] H. Wang, Y. Qu, H. Chen, Z. Lin, K. Dai, Highly selective n-butanol gas sensor based on mesoporous SnO<sub>2</sub> prepared with hydrothermal treatment, *Sensors Actuators B Chem.* 201 (2014) 153–159. <https://doi.org/10.1016/j.snb.2014.04.049>.
- [18] New Jersey Department of Health, Right to Know Hazardous Substance Fact Sheet - n-butyl alcohol, 2008. <https://www.nj.gov/health/eoh/rtkweb/documents/fs/1330.pdf>.
- [19] I.S. Maddox, Production of n-butanol from whey filtrate using clostridium acetobutylicum N.C.I.B. 2951, *Biotechnol. Lett.* 2 (1980) 493–498. <https://doi.org/10.1007/BF00129545>.
- [20] C.-L. Cheng, P.-Y. Che, B.-Y. Chen, W.-J. Lee, L.-J. Chien, J.-S. Chang, High yield bio-butanol production by solvent-producing bacterial microflora, *Bioresour. Technol.* 113 (2012) 58–64. <https://doi.org/10.1016/j.biortech.2011.12.133>.
- [21] J. Huang, Y. Wu, C. Gu, M. Zhai, K. Yu, M. Yang, J. Liu, Large-scale synthesis of flowerlike ZnO nanostructure by a simple chemical solution route and its gas-sensing property, *Sensors Actuators B Chem.* 146 (2010) 206–212. <https://doi.org/10.1016/j.snb.2010.02.052>.
- [22] O. Lupan, V. Cretu, V. Postica, N. Ababii, O. Polonskyi, V. Kaidas, F. Schütt, Y.K. Mishra, E. Monaico, I. Tiginyanu, V. Sontea, T. Strunskus, F. Faupel, R. Adelung, Enhanced ethanol vapour sensing performances of copper oxide nanocrystals with mixed phases, *Sensors Actuators B Chem.* 224 (2016) 434–448. <https://doi.org/10.1016/j.snb.2015.10.042>.

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

- [23] V. Cretu, V. Postica, A.K. Mishra, M. Hoppe, I. Tiginyanu, Y.K. Mishra, L. Chow, N.H. de Leeuw, R. Adelung, O. Lupan, Synthesis, characterization and DFT studies of zinc-doped copper oxide nanocrystals for gas sensing applications, J. Mater. Chem. A. 4 (2016) 6527–6539. <https://doi.org/10.1039/C6TA01355D>.
- [24] L.-J. Zhou, Y.-C. Zou, J. Zhao, P.-P. Wang, L.-L. Feng, L.-W. Sun, D.-J. Wang, G.-D. Li, Facile synthesis of highly stable and porous Cu<sub>2</sub>O/CuO cubes with enhanced gas sensing properties, Sensors Actuators B Chem. 188 (2013) 533–539. <https://doi.org/10.1016/j.snb.2013.07.059>.
- [25] H. Haberland, M. Karrais, M. Mall, Y. Thurner, Thin films from energetic cluster impact: A feasibility study, J. Vac. Sci. Technol. A Vacuum, Surfaces, Film. 10 (1992) 3266–3271. <https://doi.org/10.1116/1.577853>.
- [26] A. Vahl, J. Strobel, W. Reichstein, O. Polonskyi, T. Strunskus, L. Kienle, F. Faupel, Single target sputter deposition of alloy nanoparticles with adjustable composition via a gas aggregation cluster source, Nanotechnology. 28 (2017) 175703. <https://doi.org/10.1088/1361-6528/aa66ef>.
- [27] S. Veziroglu, J. Hwang, J. Drewes, I. Barg, J. Shondo, T. Strunskus, O. Polonskyi, F. Faupel, O.C. Aktas, PdO nanoparticles decorated TiO<sub>2</sub> film with enhanced photocatalytic and self-cleaning properties, Mater. Today Chem. 16 (2020) 100251. <https://doi.org/10.1016/j.mtchem.2020.100251>.
- [28] O. Lupan, V. Postica, M. Hoppe, N. Wolff, O. Polonskyi, T. Pauporté, B. Viana, O. Majérus, L. Kienle, F. Faupel, R. Adelung, PdO/PdO<sub>2</sub> functionalized ZnO:Pd films for lower operating temperature H<sub>2</sub> gas sensing, Nanoscale. 10 (2018) 14107–14127. <https://doi.org/10.1039/C8NR03260B>.
- [29] O. Lupan, V. Cretu, V. Postica, O. Polonskyi, N. Ababii, F. Schütt, V. Kaidas, F. Faupel, R. Adelung, Non-planar nanoscale p–p heterojunctions formation in Zn<sub>x</sub>Cu<sub>1-x</sub>O<sub>y</sub> nanocrystals by mixed phases for enhanced sensors, Sensors Actuators B Chem. 230 (2016) 832–843. <https://doi.org/10.1016/j.snb.2016.02.089>.
- [30] G. Kresse, J. Hafner, Ab initio molecular dynamics for liquid metals, Phys. Rev. B. 36

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

- 47 (1993) 558–561. <https://doi.org/10.1103/PhysRevB.47.558>.
- [31] G. Kresse, J. Hafner, Ab initio molecular-dynamics simulation of the liquid-metal–amorphous-semiconductor transition in germanium, Phys. Rev. B. 49 (1994) 14251–14269. <https://doi.org/10.1103/PhysRevB.49.14251>.
- [32] G. Kresse, J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, Phys. Rev. B. 54 (1996) 11169–11186. <https://doi.org/10.1103/PhysRevB.54.11169>.
- [33] G. Kresse, J. Furthmüller, Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set, Comput. Mater. Sci. 6 (1996) 15–50. [https://doi.org/10.1016/0927-0256\(96\)00008-0](https://doi.org/10.1016/0927-0256(96)00008-0).
- [34] J.P. Perdew, K. Burke, M. Ernzerhof, Generalized Gradient Approximation Made Simple [Phys. Rev. Lett. 77, 3865 (1996)], Phys. Rev. Lett. 78 (1997) 1396–1396. <https://doi.org/10.1103/PhysRevLett.78.1396>.
- [35] J.P. Perdew, K. Burke, M. Ernzerhof, Generalized Gradient Approximation Made Simple, Phys. Rev. Lett. 77 (1996) 3865–3868. <https://doi.org/10.1103/PhysRevLett.77.3865>.
- [36] S. Grimme, J. Antony, S. Ehrlich, H. Krieg, A consistent and accurate ab initio parametrization of density functional dispersion correction (DFT-D) for the 94 elements H–Pu., J. Chem. Phys. 132 (2010) 154104. <https://doi.org/10.1063/1.3382344>.
- [37] S. Grimme, S. Ehrlich, L. Goerigk, Effect of the damping function in dispersion corrected density functional theory., J. Comput. Chem. 32 (2011) 1456–1465. <https://doi.org/10.1002/jcc.21759>.
- [38] B. Farkaš, D. Santos-Carballal, A. Cadi-Essadek, N.H. de Leeuw, A DFT+U study of the oxidation of cobalt nanoparticles: Implications for biomedical applications, Materialia. 7 (2019) 100381. <https://doi.org/10.1016/j.mtla.2019.100381>.
- [39] M.J. Ungerer, D. Santos-Carballal, A. Cadi-Essadek, C.G.C.E. van Sittert, N.H. de Leeuw, Interaction of H<sub>2</sub>O with the Platinum Pt (001), (011), and (111) Surfaces: A

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

- Density Functional Theory Study with Long-Range Dispersion Corrections, J. Phys. Chem. C. 123 (2019) 27465–27476. <https://doi.org/10.1021/acs.jpcc.9b06136>.
- [40] L.M. Botha, D. Santos-Carballal, U. Terranova, M.G. Quesne, M.J. Ungerer, C.G.C.E. van Sittert, N.H. de Leeuw, Mixing thermodynamics and electronic structure of the Pt<sub>1-x</sub>Ni<sub>x</sub> (0 ≤ x ≤ 1) bimetallic alloy, RSC Adv. 9 (2019) 16948–16954. <https://doi.org/10.1039/C9RA02320H>.
- [41] D. Santos-Carballal, P.E. Ngoepe, N.H. de Leeuw, Ab initio investigation of the thermodynamics of cation distribution and of the electronic and magnetic structures in the LiMn<sub>2</sub>O<sub>4</sub> spinel, Phys. Rev. B. 97 (2018) 085126. <https://doi.org/10.1103/PhysRevB.97.085126>.
- [42] S. Posada-Pérez, D. Santos-Carballal, U. Terranova, A. Roldan, F. Illas, N.H. de Leeuw, CO<sub>2</sub> Interaction with Violarite (FeNi<sub>2</sub>S<sub>4</sub>) Surfaces: A Dispersion-Corrected DFT Study, Phys. Chem. Chem. Phys. 20 (2018) 20439–20446. <https://doi.org/10.1039/C8CP03430C>.
- [43] V. Postica, A. Vahl, J. Strobel, D. Santos-Carballal, O. Lupan, A. Cadi-Essadek, N.H. De Leeuw, F. Schütt, O. Polonskyi, T. Strunskus, M. Baum, L. Kienle, R. Adelung, F. Faupel, Tuning doping and surface functionalization of columnar oxide films for volatile organic compounds sensing: Experiments and theory, J. Mater. Chem. A. 6 (2018) 23669–23682. <https://doi.org/10.1039/C8TA08985J>.
- [44] L. Reguera, N.L. López, J. Rodríguez-Hernández, M. González, C.E. Hernandez-Tamargo, D. Santos-Carballal, N.H. de Leeuw, E. Reguera, Synthesis, Crystal Structures, and Properties of Zeolite-Like T<sub>3</sub>(H<sub>3</sub>O)<sub>2</sub>M(CN)<sub>6</sub>]<sub>2</sub>·uH<sub>2</sub>O (T=Co, Zn; M=Ru, Os), Eur. J. Inorg. Chem. 2017 (2017) 2980–2989. <https://doi.org/10.1002/ejic.201700278>.
- [45] B. Ramogayana, D. Santos-Carballal, P.A. Aparicio, M.G. Quesne, K.P. Maenetja, P.E. Ngoepe, N.H. de Leeuw, Ethylene carbonate adsorption on the major surfaces of lithium manganese oxide Li<sub>1-x</sub>Mn<sub>2</sub>O<sub>4</sub> spinel (0.000 < x < 0.375): a DFT+ *U*-D3 study, Phys. Chem. Chem. Phys. 22 (2020) 6763–6771.

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

<https://doi.org/10.1039/C9CP05658K>.

- [46] P.E. Blöchl, Projector augmented-wave method, Phys. Rev. B. 50 (1994) 17953–17979. <https://doi.org/10.1103/PhysRevB.50.17953>.
- [47] G. Kresse, D. Joubert, From ultrasoft pseudopotentials to the projector augmented-wave method, Phys. Rev. B. 59 (1999) 1758–1775. <https://doi.org/10.1103/PhysRevB.59.1758>.
- [48] D. Sheppard, R. Terrell, G. Henkelman, Optimization methods for finding minimum energy paths., J. Chem. Phys. 128 (2008) 134106. <https://doi.org/10.1063/1.2841941>.
- [49] M.R. Hestenes, E. Stiefel, Methods of conjugate gradients for solving linear systems, J. Res. Natl. Bur. Stand. (1934). 49 (1952) 409. <https://doi.org/10.6028/jres.049.044>.
- [50] V.I. Anisimov, M.A. Korotin, J. Zaanen, O.K. Andersen, Spin bags, polarons, and impurity potentials in La<sub>2-x</sub>Sr<sub>x</sub>CuO<sub>4</sub> from first principles, Phys. Rev. Lett. 68 (1992) 345–348. <https://doi.org/10.1103/PhysRevLett.68.345>.
- [51] S.L. Dudarev, G.A. Botton, S.Y. Savrasov, C.J. Humphreys, A.P. Sutton, Electron-energy-loss spectra and the structural stability of nickel oxide: An LSDA+*U* study, Phys. Rev. B. 57 (1998) 1505–1509. <https://doi.org/10.1103/PhysRevB.57.1505>.
- [52] I. de P.R. Moreira, F. Illas, R.L. Martin, Effect of Fock exchange on the electronic structure and magnetic coupling in NiO, Phys. Rev. B. 65 (2002) 155102. <https://doi.org/10.1103/PhysRevB.65.155102>.
- [53] C.E. Calderon, J.J. Plata, C. Toher, C. Oses, O. Levy, M. Fornari, A. Natan, M.J. Mehl, G. Hart, M. Buongiorno Nardelli, S. Curtarolo, The AFLOW standard for high-throughput materials science calculations, Comput. Mater. Sci. 108 (2015) 233–238. <https://doi.org/10.1016/j.commatsci.2015.07.019>.
- [54] W. Setyawan, S. Curtarolo, High-throughput electronic band structure calculations: Challenges and tools, Comput. Mater. Sci. 49 (2010) 299–312. <https://doi.org/10.1016/j.commatsci.2010.05.010>.



*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

- [55] W. Setyawan, R.M. Gaume, S. Lam, R.S. Feigelson, S. Curtarolo, High-throughput combinatorial database of electronic band structures for inorganic scintillator materials, *ACS Comb. Sci.* 13 (2011) 382–390. <https://doi.org/10.1021/co200012w>.
- [56] S. Wang, Z. Wang, W. Setyawan, N. Mingo, S. Curtarolo, Assessing the Thermoelectric Properties of Sintered Compounds via High-Throughput Ab-Initio Calculations, *Phys. Rev. X.* 1 (2011) 1–8. <https://doi.org/10.1103/PhysRevX.1.021012>.
- [57] R.H. Taylor, F. Rose, C. Toher, O. Levy, K. Yang, M. Buongiorno Nardelli, S. Curtarolo, A RESTful API for exchanging materials data in the AFLOWLIB.org consortium, *Comput. Mater. Sci.* 93 (2014) 178–192. <https://doi.org/10.1016/j.commatsci.2014.05.014>.
- [58] O.K. Andersen, Electronic structure of the fcc transition metals Ir, Rh, Pt, and Pd, *Phys. Rev. B.* 2 (1970) 883–906. <https://doi.org/10.1103/PhysRevB.2.883>.
- [59] W. Speier, J.C. Fuggle, R. Zeller, B. Ackermann, K. Szot, F.U. Hillebrecht, M. Campagna, Bremsstrahlung isochromat spectra and density-of-states calculations for the 3d and 4d transition metals, *Phys. Rev. B.* 30 (1984) 6921–6930. <https://doi.org/10.1103/PhysRevB.30.6921>.
- [60] H.J. Monkhorst, J.D. Pack, Special points for Brillouin-zone integrations, *Phys. Rev. B.* 13 (1976) 5188–5192. <https://doi.org/10.1103/PhysRevB.13.5188>.
- [61] M. Methfessel, A.T. Paxton, High-precision sampling for Brillouin-zone integration in metals, *Phys. Rev. B.* 40 (1989) 3616–3621. <https://doi.org/10.1103/PhysRevB.40.3616>.
- [62] N.D. Mermin, Thermal Properties of the Inhomogeneous Electron Gas, *Phys. Rev.* 137 (1965) A1441–A1443. <https://doi.org/10.1103/PhysRev.137.A1441>.
- [63] P.E. Blöchl, O. Jepsen, O.K. Andersen, Improved tetrahedron method for Brillouin-zone integrations, *Phys. Rev. B.* 49 (1994) 16223–16233. <https://doi.org/10.1103/PhysRevB.49.16223>.
- [64] W. Li, X. Yan, A.G. Aberle, S. Venkataraj, Effect of sodium diffusion on the

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

- properties of CIGS solar absorbers prepared using elemental Se in a two-step process, Sci. Rep. 9 (2019) 2637. <https://doi.org/10.1038/s41598-019-39283-2>.
- [65] J.-T. Fonné, E. Burov, E. Gouillart, S. Grachev, H. Montigaud, D. Vandembroucq, Interdiffusion between silica thin films and soda-lime glass substrate during annealing at high temperature, J. Am. Ceram. Soc. 102 (2019) 3341–3353. <https://doi.org/10.1111/jace.16154>.
- [66] J.F. Moulder, W.F. Stickle, P.E. Sobol, K.D. Bomben, Handbook of X-ray Photoelectron Spectroscopy (Perkin-Elmer, Eden Prairie, MN, 1992), Google Sch. (2002) 128.
- [67] C.J.P. Alexander V. Naumkin, Anna Kraut-Vass, Stephen W. Gaarenstroom, NIST X-ray Photoelectron Spectroscopy Database, National Institute of Standards and Technology, NIST Stand. Ref. Database Number 20. (2000) 20899, NIST X-Ray Photoelectron Spectrosc. Database, NIST Stand. Ref. Database 20, Version 4.1. (2000) Accessed: 2018-02-08. <https://doi.org/10.18434/T4T88K>.
- [68] A. Sahai, N. Goswami, S.D. Kaushik, S. Tripathi, Cu/Cu<sub>2</sub>O/CuO nanoparticles: Novel synthesis by exploding wire technique and extensive characterization, Appl. Surf. Sci. 390 (2016) 974–983. <https://doi.org/10.1016/j.apsusc.2016.09.005>.
- [69] K.A. Willets, R.P. Van Duyne, Localized Surface Plasmon Resonance Spectroscopy and Sensing, Annu. Rev. Phys. Chem. 58 (2007) 267–297. <https://doi.org/10.1146/annurev.physchem.58.032806.104607>.
- [70] J.R. Ferraro, K. Nakamoto, Basic Theory, in: J.R. Ferraro, K.B.T.-I.R.S. Nakamoto (Eds.), Introd. Raman Spectrosc., Elsevier, Boston, 1994: pp. 1–94. <https://doi.org/10.1016/B978-0-12-253990-9.50005-7>.
- [71] C.K. Law, Resonance Response of the Quantum Vacuum to an Oscillating Boundary, Phys. Rev. Lett. 73 (1994) 1931–1934. <https://doi.org/10.1103/PhysRevLett.73.1931>.
- [72] F. Wooten, Optical properties of solids, (1972). <http://cds.cern.ch/record/268948>.
- [73] A.E. Rakhshani, Preparation, characteristics and photovoltaic properties of cuprous

*Cite this paper as: O Lupan, N. Ababii, D. Santos-Carballal, M.-I. Terasa; N. Magariu; D. Zappa, E. Comini, Th. Pauporté, L. Siebert, F. Faupel, A. Vahl, S. Hansen, N. H de Leeuw, R. Adelung, Tuning the Reactivity of Ultralow Power Heterojunction Sensors toward H<sub>2</sub> and VOCs through Noble Metal Nanoparticle Functionalization. NanoEnergy, 88 (2021) 106241*

- oxide—a review, Solid. State. Electron. 29 (1986) 7–17.  
[https://doi.org/10.1016/0038-1101\(86\)90191-7](https://doi.org/10.1016/0038-1101(86)90191-7).
- [74] B. Balamurugan, I. Aruna, B.R. Mehta, S.M. Shivaprasad, Size-dependent conductivity-type inversion in Cu<sub>2</sub>O nanoparticles, Phys. Rev. B. 69 (2004) 165419.  
<https://doi.org/10.1103/PhysRevB.69.165419>.
- [75] V. Postica, A. Vahl, N. Magariu, M.-I. Terasa, M. Hoppe, B. Viana, P. Aschehoug, T. Pauporté, I. Tiginyanu, O. Polonskyi, V. Sontea, L. Chow, L. Kienle, R. Adelung, F. Faupel, O. Lupan, Enhancement in UV Sensing Properties of ZnO:Ag Nanostructured Films by Surface Functionalization with Noble Metallic and Bimetallic Nanoparticles, J. Eng. Sci. XXV (2018) 41–51.  
<https://doi.org/10.5281/zenodo.2557280>.
- [76] M. Mathew, P. V Shinde, R. Samal, C.S. Rout, A review on mechanisms and recent developments in p-n heterojunctions of 2D materials for gas sensing applications, J. Mater. Sci. 56 (2021) 9575–9604. <https://doi.org/10.1007/s10853-021-05884-4>.
- [77] H. Xuemei, S. Yukun, B. Bo, Fabrication of Cubic p-n Heterojunction-Like NiO/In<sub>2</sub>O<sub>3</sub> Composite Microparticles and Their Enhanced Gas Sensing Characteristics, J. Nanomater. 2016 (2016) 1–9.  
<https://doi.org/10.1155/2016/7589028>.
- [78] D.E.P. Vanpoucke, G. Brocks, Formation of Pt-induced Ge atomic nanowires on Pt/Ge(001): A density functional theory study, Phys. Rev. B. 77 (2008) 241308.  
<https://doi.org/10.1103/PhysRevB.77.241308>.
- [79] J. Tersoff, D.R. Hamann, Theory of the scanning tunneling microscope, Phys. Rev. B. 31 (1985) 805–813. <https://doi.org/10.1103/PhysRevB.31.805>.