



**HAL**  
open science

## Niobium oxide (Nb<sub>2</sub>O<sub>5</sub>) as support for CoMo and NiW catalysts in the hydrodesulfurization reaction of 3-methylthiophene

Roberta Lopes Do Rosário, Ronaldo Costa Santos, Alan Silva Dos Santos, Alexandre Carvalho, Sylvette Brunet, Luiz Antônio Magalhães Pontes

► **To cite this version:**

Roberta Lopes Do Rosário, Ronaldo Costa Santos, Alan Silva Dos Santos, Alexandre Carvalho, Sylvette Brunet, et al.. Niobium oxide (Nb<sub>2</sub>O<sub>5</sub>) as support for CoMo and NiW catalysts in the hydrodesulfurization reaction of 3-methylthiophene. *Research, Society and Development*, 2020, 9 (11), pp.e74391110307. 10.33448/rsd-v9i11.10307 . hal-03385638

**HAL Id: hal-03385638**

**<https://hal.science/hal-03385638>**

Submitted on 19 Oct 2021

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

**Niobium oxide (Nb<sub>2</sub>O<sub>5</sub>) as support for CoMo and NiW catalysts in the  
hydrodesulfurization reaction of 3-methylthiophene**

**Avaliação de Catalisadores CoMo e NiW suportados em Óxido de Nióbio em reação de  
Hidrodesulfurização de 3-metiltiofeno**

**Evaluación de Catalizadores de CoMo y NiW soportados em Óxido de Niobio em  
Reacción de Hidrodesulfuración de 3-metiltiofeno**

Received: 11/24/2020 | Reviewed: 11/25/2020 | Accept: 11/27/2020 | Published: 12/02/2020

**Roberta Lopes do Rosário**

ORCID: <https://orcid.org/0000-0001-7041-1428>

Universidade Federal da Bahia, Brazil

E-mail: robertta.rosario@outlook.com

**Ronaldo Costa Santos**

ORCID: <https://orcid.org/0000-0002-3972-8061>

Centro Universitário Jorge Amado, Brazil

E-mail: ronaldo.ead@gmail.com

**Alan Silva dos Santos**

ORCID: <https://orcid.org/0000-0002-1200-7766>

Universidade Federal da Bahia, Brazil

E-mail: alan.ss29@gmail.com

**Alexandre Carvalho**

ORCID: <https://orcid.org/0000-0003-2333-9114>

Université de Poitiers, França

E-mail: alexandre.carvalho@univ-poitiers.fr

**Sylvette Brunet**

ORCID: <https://orcid.org/0000-0003-0658-9859>

Université de Poitiers, França

E-mail: sylvette.brunet@univ-poitiers.fr

**Luiz Antônio Magalhães Pontes**

ORCID: <https://orcid.org/0000-0003-4158-4033>

Universidade Federal da Bahia, Brazil

E-mail: uolpontes@uol.com.br

## Abstract

The efficiency of niobium oxide as catalytic support of hydrodesulfurization (HDS) catalysts (CoMo and NiW) has been investigated in the HDS of a model molecule representative of sulfur compounds present in FCC gasoline (3-methylthiophene: 3MT). The NiW catalyst presented higher catalytic activity than CoMo calcined and non-calcined catalyst, however a better ratio pentane/pentene has been achieved by CoMo catalysts, which implies a lower formation of hydrogenated products. Indeed, the activity order for the catalysts evaluated is: NiW/Nb<sub>2</sub>O<sub>5</sub> > CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined support > CoMo/Nb<sub>2</sub>O<sub>5</sub> non-calcined support, despite the ratio pentane/pentene which has the inverse order. Furthermore, textural and chemical characterization techniques have been performed. From NH<sub>3</sub>-TPD analysis it was observed an acidity profile with a predominance of weak/strong and weak/moderate acid for CoMo and NiW catalysts, respectively. Meanwhile, the BET analysis has shown a low specific surface area for the catalysts supported by niobium oxide. Concerning the structure characteristic, the XRD analysis has suggested an amorphous phase in all catalysts analyzed.

**Keywords:** Hydrodesulfurization; FCC gasoline; 3-Methylthiophene; Niobium oxide; Interaction metal-support.

## Resumo

A eficiência de óxido de nióbio como suporte para catalisadores de hidrodesulfurização (HDS), CoMo e NiW, foi investigada na reação de HDS de uma molécula modelo representativa de compostos sulfurados presente na gasolina de FCC (3-metiltiofeno). O catalisador NiW/Nb<sub>2</sub>O<sub>5</sub> apresentou a maior atividade catalítica, seguido pelo catalisador CoMo/Nb<sub>2</sub>O<sub>5</sub> calcinado e por fim o catalisador CoMo/Nb<sub>2</sub>O<sub>5</sub> não calcinado. Entretanto, apesar da menor atividade catalítica, o catalisador CoMo/Nb<sub>2</sub>O<sub>5</sub> apresentou uma melhor razão pentano/penteno, fato que implica em uma menor formação de produtos hidrogenados. Além disso, caracterizações químicas e texturais foram realizadas a fim de investigar a estrutura dos catalisadores preparados. A partir da análise de TPD-NH<sub>3</sub> observa-se um perfil de acidez com predominância de ácidos fracos/fortes e fracos/moderados para os catalisadores CoMo e NiW, respectivamente. A análise de área superficial específica (BET) apresentou uma baixa área específica em todos os catalisadores CoMo e NiW, devido principalmente a baixa área superficial do óxido de nióbio. Por fim, a análise estrutural por difração de Raio-X (DRX) sugere que os catalisadores preparados não possuem uma forma cristalina.

**Palavras-chave:** Hidrodesulfurização; Gasolina de FCC; 3-Metiltiofeno; Óxido de Nióbio; Interação metal-suporte.

## Resumen

La eficiencia del óxido de niobio como soporte para catalizadores de hidrodesulfuración (HDS), CoMo y NiW, se investigó en la reacción HDS de una molécula modelo representativa de los compuestos de azufre presentes en la gasolina FCC (3-metiltiofeno). El catalizador NiW/Nb<sub>2</sub>O<sub>5</sub> mostró la mayor actividad catalítica, seguido por el catalizador CoMo/Nb<sub>2</sub>O<sub>5</sub> calcinado y el catalizador CoMo/Nb<sub>2</sub>O<sub>5</sub> no calcinado. Sin embargo, a pesar de la menor actividad catalítica, el catalizador CoMo/Nb<sub>2</sub>O<sub>5</sub> mostró una mejor relación pentano/penteno, hecho que implica una menor formación de productos hidrogenados. Además, se llevaron a cabo caracterizaciones químicas y de textura para investigar la estructura de los catalizadores preparados. A partir del análisis de TPD-NH<sub>3</sub> se observa un perfil de acidez con predominio de ácidos débiles/fuertes y débiles/moderados para los catalizadores de CoMo y NiW, respectivamente. El análisis del área superficial específica (BET) mostró un área específica baja en todos los catalizadores CoMo y NiW, principalmente debido a la baja área superficial del óxido de niobio. Finalmente, el análisis estructural por difracción de rayos X (DRX) sugiere que los catalizadores preparados no tienen forma cristalina.

**Palabras clave:** Hidrodesulfuración; Gasolina FCC; 3-Metiltiofeno; Óxido de Nióbio; Interacción metal-soporte.

## 1. Introduction

The reduction of pollutants in fossil fuels is a challenge in the refineries taking into account more strict regulations and the development of environmentally friendly energy. In order to achieve the requirement for environmental regulations, different alternatives need to be evaluated aiming at reducing contaminants present in the motor vehicle fuels (Lu et al., 2020; Santos et al., 2019). Hydrotreatment process is one of the alternatives and consists in removing impurities (S, N, O) from crudes under high partial pressure of hydrogen. Regarding the hydrodesulfurization process of FCC gasoline, the challenge is to selectively hydrodesulfurize the sulfur species (HDS) and to avoid the hydrogenation of olefins (HYD) in order to preserve the octane number of the fuel (Silva & Secchi, 2018).

Due to the presence of sulfur compounds, the hydrotreatment process needs specific catalysts that combine high thioresistance and catalytic activity. In this regard, hydrotreating catalysts are usually in form of transition metal sulfides (TMS) such as molybdenum and tungsten (VIB group) promoted by elements of VIIB group such as nickel or cobalt and

supported on alumina, silica or aluminosilicates. Thus, the usual industrial catalyst for the hydrodesulfurization processes is the molybdenum sulfide catalysts promoted by nickel or cobalt, depending on the feed to be hydrotreated, with a Co(Ni)/[Co(Ni)+Mo] molar ratio between 0.3-0.6 (Santos et al., 2019). Furthermore, the catalytic support is responsible for loading the active components and disperse the active phase, improving the reaction effectiveness. It is the catalytic support that influences the diffusion, adsorption and determines the accessibility of reactants towards the active sites (Gutierrez et al., 2017; Huirache-Acuña et al., 2012). This fact presents the relevant importance of the support and the interaction metal-support in the preparation step of a hydrotreatment catalyst.

Currently, Brazil has more than 90% of the world's natural resource of niobium (Nb) and it is considered the largest explorer country in the world for this metal. In the hydrotreatment field, the literature has shown an increase in the number of publications about activity and selectivity enhancement as well as the chemical stability of traditional catalysts when a small amount of niobium is added (Aray et al., 2014; Méndez et al., 2017). Gaborit et al. (2000) used niobium as a dopant for hydrotreating NiMo catalyst to investigate the hydrodesulfurization of dibenzothiophene (DBT) and hydrogenation (HYD) of tetraline at  $P = 33$  bar and  $T = 300^{\circ}\text{C}$ . The use of niobium as a dopant has increased the catalytic activity in both, HDS and HYD, model reactions where the highest activities were obtained with an optimum niobium content of 5%. In the case of DBT hydrodesulfurization, the selectivity for cracked products increased and isoalkylbenzenes appeared when Nb was added, which demonstrated that niobium sulfide enhanced the catalytic acidic properties. Since then, a crescent interest in the application of these materials has been noticed, especially with studies about niobium oxides as active phase or catalytic support. The  $\text{Nb}_2\text{O}_5$  has already been used as support to Mo and Co (Ni) Mo as well as a precursor of active phase such as niobium sulfide (Faro et al., 2006; Kaluza & Zdražil, 2018; Méndez et al., 2017). For instance, Faro et al. (2006) have investigated the HDS of thiophene at 2.8 MPa and 523–573 K and concluded that the degree of niobium sulfidation increases in the following order:  $\text{Nb}_2\text{O}_5 < \text{Ni}/\text{Nb}_2\text{O}_5 < \text{Mo}/\text{Nb}_2\text{O}_5 < \text{NiMo}/\text{Nb}_2\text{O}_5$ . Moreover, it was concluded that niobium sulfide has a strong influence on the activity of the niobium-supported catalysts in the cumene hydrocracking reaction.

Furthermore, the selective hydrodesulfurization reaction has also been studied over supported tungsten catalyst promoted by nickel under specific operating conditions, due mainly to the promising HDS activity over the  $\text{WS}_2$  slabs. Indeed, León et al. (2017) have studied the HDS of 3-methylthiophene at  $T = 280^{\circ}\text{C}$  and atmospheric pressure over a

supported NiW catalyst under different supports. In this study, the catalytic performance of the NiW was attributed to an efficient metal-support interaction, particularly with the samples that used the proposed mixed supports.

In order to further increase the catalytic activity through enhancing the interaction of metallic ions, numerous studies have been published in the literature by using a chelating agent in the hydrotreatment catalysts (CoMo and NiMo, NiW) preparation (Haandel et al., 2017; Pereyma et al., 2018; Valencia et al., 2014; Valencia & Klimova, 2012). The chelating agent are molecules composed by two or more atoms donors of electrons that works as a ligand of a metallic ion behaving as acid/base of Lewis. This reaction occurs with a great contribution of entropy, due to the water molecules surrounding of metallic ion replaced by a ligand chelating (Kaluza et al., 2012). In the literature, the citric acid and ethylene diamino tetracetic acid (EDTA) have been studied as a chelating agent in the in the preparation step of catalysts for hydrotreatment of sulfur compounds such as thiophene and benzothiophene with NiMo, CoMo and NiW catalysts (Castillo-villalón et al., 2014; Kaluza & Zdražil, 2018; Lélías et al., 2010; Pereyma et al., 2018). Indeed, Kaluza & Zdražil (2018) have applied the nitrilotriacetic acid (NTA) in the preparation of CoMo catalyst supported in niobium in order to improve its activity in the HDS of thiophene at 1.0 MPa and 400°C. A pronounced improvement (5.7 times) has been noticed when compared the specific activity normalized per total BET surface area with the commercial catalyst, which was attributed to a positive effect of NTA in the preparation of supported niobium catalyst as well as the high activity per m<sup>2</sup> of CoMo/Nb<sub>2</sub>O<sub>5</sub> catalyst. The citric acid as a chelating agent was also used in the preparation of a supported NiW catalyst in the investigation of the effect of catalytic thermal treatment in the HDS of dibenzothiophene (T = 280°C, P = 35 bar, H<sub>2</sub>/feed = 500 m<sup>3</sup>/m<sup>3</sup>) (Pereyma et al., 2018). In this study, a direct correlation between the thermal treatment temperature and the catalytic activity of DBT HDS has been found and attributed to an increasing in the stacking degree of WS<sub>2</sub> while maintaining a small length of sulfide slabs.

This paper focuses on the efficiency of niobium oxide as a support for two types of catalysts, CoMo and NiW, in the hydrodesulfurization of a model sulfur molecule (3-methylthiophene) representative of sulfur species present in the FCC gasoline. The role of the support as well as the active phase will be investigated through a catalytic activity test and explained by the proposed characterizations aiming at achieving the selective hydrodesulfurization of model molecule by avoiding the hydrogenation of olefins.

## 2. Experimental Part

### 2.1 Catalyst and chemicals

The CoMo catalyst precursors were prepared using Ammonium Heptamolybdate Tetrahydrate - AHM (Sigma Aldrich, Prod. No.1.01182) and cobalt nitrate hexahydrate - CoN (Vetec, Prod. No. 295). Meanwhile, the NiW were prepared with Ammonium Metatungstate - AM (Sigma Aldrich, Prod. No. 463922) and Nickel Nitrate - NiN (Sigma Aldrich, Prod. No. 301100025414). The Citric Acid - CA (Sigma Aldrich, Prod. No.1001727327) was used as a chelating agent in the preparation of both types of catalysts (CoMo and NiW). Niobium oxide hydrate ( $\text{Nb}_2\text{O}_5 \cdot x\text{H}_2\text{O}$ ) was provided by Companhia Brasileira de Metalurgia e Mineração in the form of fine powder.

The support for the catalysts ( $\text{Nb}_2\text{O}_5$ ) has been calcined in a muffle for 4 hours at 400°C. Afterward, the sample was used for metal wet impregnation with a molar ratio CA/precursor = 1. The mass of precursors as well as the molar ratio Co:Mo and Ni:W for the catalysts prepared are presented in Table 1.

**Table 1.** Theoretical mass of precursors and the molar ratio of each metal used in the catalyst preparation.

Compound	CoMo/ $\text{Al}_2\text{O}_3$ <sup>1</sup>	CoMo/ $\text{Nb}_2\text{O}_5$ non calcined support	CoMo/ $\text{Nb}_2\text{O}_5$ calcined support	NiW/ $\text{Nb}_2\text{O}_5$ calcined support
CoO (wt%)	3.0	3.2	3.2	-
MoO <sub>3</sub> (wt%)	10.0	15.5	15.5	-
NiO (wt%)	-	-	-	3.8
WO <sub>3</sub> (wt%)	-	-	-	24.5
Citric Acid (wt%)	-	17.4	17.4	11.0
Molar Ratio $(A/(A+B))^2$	0.35	0.21	0.21	0.26

1. (Santos et al., 2019)

2. Where: A: Co or Ni; B: Mo or W.

Source: Authors.

The supported CoMo and NiW over  $\text{Nb}_2\text{O}_5$  were prepared by wet impregnation with an aqueous solution of the precursor of CA, CoN and AHM for CoMo and CA, AM and NiN

for NiW. The pH of each sample was 2.70 for the non-calcinated support, 1.38 for the CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined support and 1.15 for the CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined support.

In all samples, the wet impregnation resulted in a solid catalyst that was dried in a rotary vacuum evaporator for 1h and in the oven at 110°C for 2h. The catalyst was crushed and sieved to a size range between 250 and 315 µm and then sulfided *in situ* under H<sub>2</sub>S/H<sub>2</sub> flow (10 mol% H<sub>2</sub>S) for 10 h at 400°C and atmospheric pressure. 3-methylthiophene (98% purity) and n-heptane (>99% purity) were purchased from Sigma-Aldrich which was used without further purification. Hydrogen sulfide (1 vol% in mixture with H<sub>2</sub>) was purchased from Air Liquide.

## 2.2 Characterization techniques

The specific surface area of the catalysts was measured on a Micromeritics ASAP 2000 analyzer at -196°C. Before N<sub>2</sub> adsorption, the solid samples containing oxide precursors were degassed overnight under a secondary vacuum at 120°C. The specific surface area (S<sub>BET</sub> in m<sup>2</sup>/g) was calculated from the adsorption isotherm (P/P<sub>0</sub> between 0.05 and 0.20) using the Brunauer-Emmett-Teller (BET) method. The total pore volume was calculated from the adsorbed volume of nitrogen at P/P<sub>0</sub> equal to 0.99.

The acidity of the catalyst was measured by the NH<sub>3</sub>-TPD technique. The samples (150 mg) were pretreated with He (30 mL/min) at 200 °C for 30 min and cooled down to 100 °C. The ammonia adsorption was then carried out (5% NH<sub>3</sub> in He: 30 mL/min, for 30 min). The physisorbed ammonia was purged with He (30 mL/min) for 1 h. The desorption of NH<sub>3</sub> was measured from 100°C to 400°C with a rate of 5 °C.min<sup>-1</sup> under the inert gas helium. The amount of desorbed NH<sub>3</sub> was analyzed using a TCD detector.

The decomposition temperature of the precursor as well as the stability of the support was evaluated by thermogravimetric analysis, using a thermobalance from Shimadzu model DTG-60 by heating (5mg) the sample between 25-900 °C (rate of 10 °C/min) under a nitrogen flow rate of 100 mL/min.

The crystallinity of the various samples was determined by X-ray diffraction (XRD), using Shimadzu model XRD 6100 diffractometer with a Cu-Kα tube at 40 kV and 30 mA, with a sample drawer specific for powder-like material. The diffractograms were obtained in the 2θ range between 5 and 80°, with a scanning speed of 2° min<sup>-1</sup> and 0.02° step at every 0.6s.



### **2.3. Reaction conditions**

Catalytic activity measurements were carried out in a fixed bed reactor at 250°C under a total pressure of 2 MPa with a ratio H<sub>2</sub>/feed of 360 NL/L. The sulfur model feed (0.3wt% of 3-methylthiophene), containing 1000 ppmS in n-heptane was injected in the reactor by an HPLC Gilson pump (307 series, pump's head volume: 5 cm<sup>3</sup>). The mass of catalyst used was between 200 and 300 mg. The reaction products were injected on-line using an automatic sampling valve into a Varian gas chromatograph equipped with a PONA capillary column and a flame ionization detector as in previous works (Daudin et al., 2007; Lamic et al., 2008; Naboulsi et al., 2018; Pelardy et al., 2016, 2017; Santos et al., 2019). Desulfurized products, resulting from the transformation of 3-methylthiophene are designated as HDS products corresponding also under these operating conditions to the conversion. The contact time is defined as the ratio between the total amount of feed and the mass of catalyst in the oxide form. The catalytic activity was calculated as the number of moles of HDS products formed per hour and per gram of catalyst. This parameter was calculated at a conversion lower than 30% in a differential regime.

### **2.4. Scientific Methodology**

The scientific methodology of this work was focused on the comparative method since different catalysts have been evaluated and compared in different aspects from catalytic activity until the product distribution in a scope of laboratory research. According to Pereira et al. (2018) the nature of this study is focused on the quantitative methodology since the data have been collected from experimental results, treated and analyzed comparatively.

## **3. Results**


### **3.1. Catalyst Characterization**

The physical-chemical properties of the different catalysts CoMo/Nb<sub>2</sub>O<sub>5</sub> and NiW/Nb<sub>2</sub>O<sub>5</sub> were characterized by their mass loss, specific surface area, structure and acidity measured by TGA, BET, XRD and NH<sub>3</sub>-TPD, respectively.

The thermogravimetric analysis has shown endothermic and exothermic phenomena for the three catalyst samples with and/or without a mass loss (Figure 1). The phenomena observed from room temperature up to 150°C is attributed to mass loss due to the removal of water physically adsorbed in the oxide structure (Silva et al., 2000). The second phenomenon

observed at 550°C and 660°C, without significant mass loss, could be correlated to the formation of crystal phase Nb<sub>2</sub>O<sub>5</sub> with a pseudo-hexagonal structure, in accordance to the results obtained by Falk et al. (2014). Regarding the non-calcined CoMo/Nb<sub>2</sub>O<sub>5</sub> catalyst it is possible to notice a peak, of exothermic nature, related to mass losses at 150°C and 220°C (Figure 1a) attributed to thermal decomposition of precursor salts of Co and Mo present in the metal impregnation process. Meanwhile, for the CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined support catalyst (Figure 1b), it was observed a thermal decomposition in different steps. Indeed, the decomposition peaks occur at 400°C and 425°C, with exothermic nature, corresponding to a multiple-step of decomposition for the formation of different Co and Mo oxides (Gonzalez-Cortes et al., 2014; Salazar et al., 2017). Finally, for the NiW/Nb<sub>2</sub>O<sub>5</sub> catalyst (Figure 1c), an exothermic event at 350°C, with mass loss is observed, which could be attributed to the formation of different Ni and W oxides on the niobium surface.

**Figure 1.** Thermogravimetric Analysis for a) CoMo/Nb<sub>2</sub>O<sub>5</sub> non calcined support; b) CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined support; c) NiW/Nb<sub>2</sub>O<sub>5</sub> calcined support.

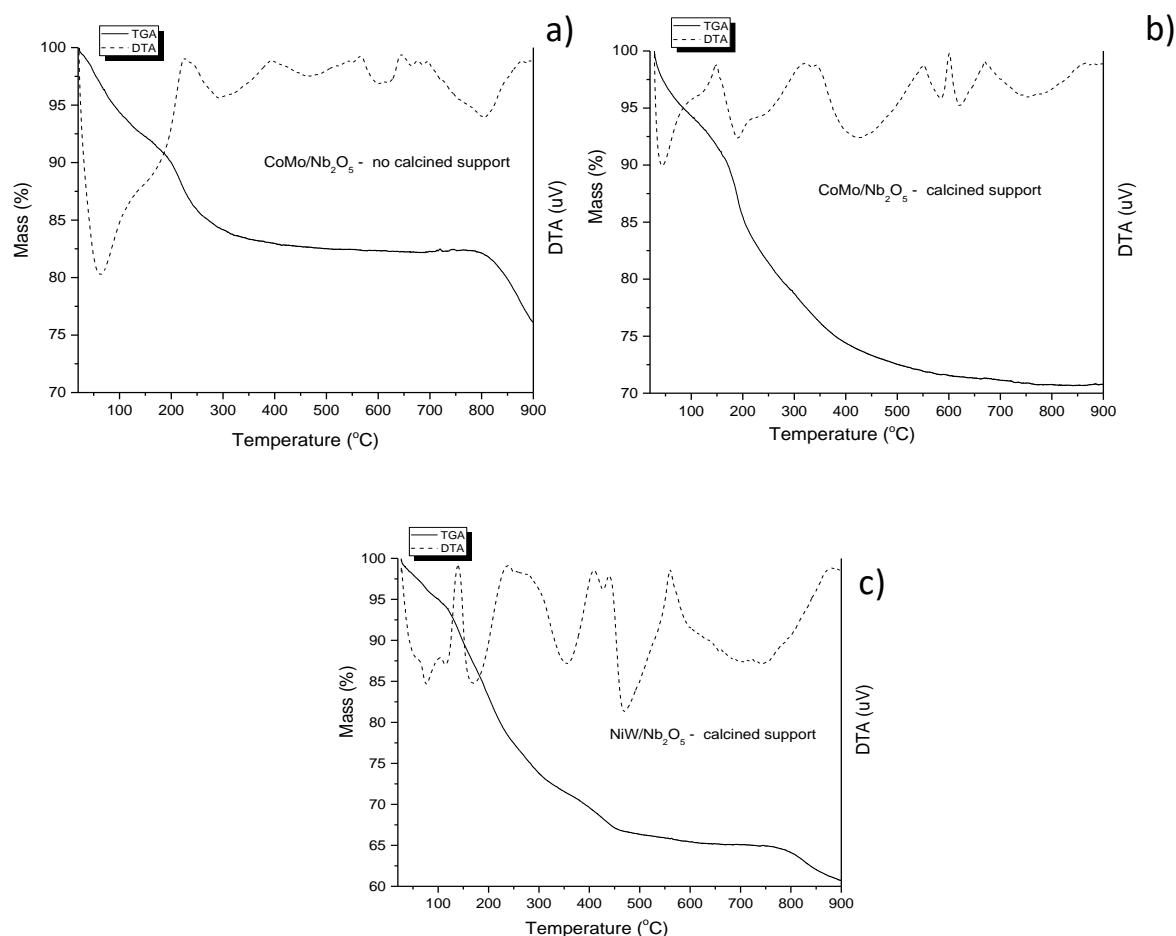

Fonte: Authors.

The specific surface areas are very low excepted for the CoMo/Nb<sub>2</sub>O<sub>5</sub> non-calcined support catalyst (29 m<sup>2</sup>/g) (Table 2). Indeed, after the calcination step at 400°C, the specific surface area of CoMo/Nb<sub>2</sub>O<sub>5</sub> and NiW/Nb<sub>2</sub>O<sub>5</sub> calcined catalysts are 6 and 2 m<sup>2</sup>/g, respectively corresponding possibly to the decomposition of precursors as shown by TGA-DTA technique. Furthermore, the loss of area could also be correspondent to the partial blocked of the pores by the presence of oxides.


**Table 2.** NH<sub>3</sub>-TPD desorption and BET surface area determined for different catalysts.

Catalyst	NH <sub>3</sub> (μmol/g)				strong/ (moderate+weak) ratio	SBET (m <sup>2</sup> /g)
	Total	weak	moderate	strong		
CoMo/Nb <sub>2</sub> O <sub>5</sub> - non calcined support	383	173 (45%)	53 (14%)	157 (41%)	0.7	29
CoMo/Nb <sub>2</sub> O <sub>5</sub> - calcined support	380	57 (15%)	105 (28%)	218 (57%)	1.3	6
NiW/Nb <sub>2</sub> O <sub>5</sub> - calcined support	411	151 (37%)	177 (43%)	83 (20%)	0.3	2

Fonte: Authors.

XRD results of the non-calcined and calcined support catalysts presented an amorphous structure. In all catalyst samples, it was observed two wide peaks at  $2\theta = 25^\circ$  and  $52^\circ$  which is characteristic of a niobium amorphous phase. The intensity and shape of the peaks observed in Figure 2 suggest that there is not a defined crystallinity structure or the particles are well dispersed that they could not be noticed in the X-Ray Diffraction. Indeed, the results of these three samples are in accordance with the Nb<sub>2</sub>O<sub>5</sub> phase observed by Santos et al. (2017). Furthermore, the patterns observed for the calcined and non-calcined CoMo/Nb<sub>2</sub>O<sub>5</sub> have suggested that even with the support calcination step, the Nb<sub>2</sub>O<sub>5</sub> structure has been maintained.


**Figure 2.** X-Ray Diffraction of the catalysts prepared (CoMo/Nb<sub>2</sub>O<sub>5</sub> non-calcined support, CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined support and NiW/Nb<sub>2</sub>O<sub>5</sub> calcined support).

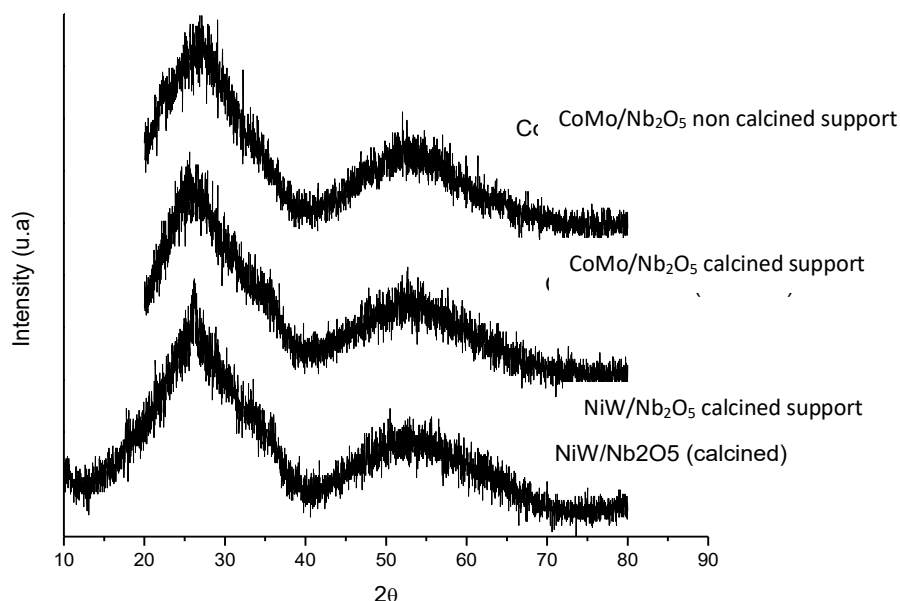

Fonte: Authors.

Finally, the total acidity of different samples has been investigated through the NH<sub>3</sub>-TPD. As reported in Figure 3, representing the curve of NH<sub>3</sub> desorption as a function of time and temperature, it can be seen that, whatsoever the catalysts, various peaks were observed corresponding to different acidity strengths. Indeed, it is noticed that for the CoMo/Nb<sub>2</sub>O<sub>5</sub> non-calcined support catalyst (Figure 3a) weak and strong acid sites are predominant whereas for the CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined catalyst (Figure 3b) there are mainly moderate and still more relevant strong acid sites. Indeed, the literature suggests that the enhancement of temperature promotes a decrease of acidity, creating new superficial sites with different acid strengths and modifying the material properties as an ion exchanger (Kitano et al., 2012). Regarding the NiW/Nb<sub>2</sub>O<sub>5</sub> catalyst (Figure 3c) there is an important predominance of weak and moderate acid sites (37 and 43%, respectively), confirming a weaker acidity of NiW in comparison with CoMo catalysts. These results and proportions of acidity strength between the catalysts are also presented in Table 2.

**Figure 3.** NH<sub>3</sub> Desorption as a function of temperature for: a) CoMo/Nb<sub>2</sub>O<sub>5</sub> non-calcined support, b) CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined support and c) NiW/Nb<sub>2</sub>O<sub>5</sub> catalysts.

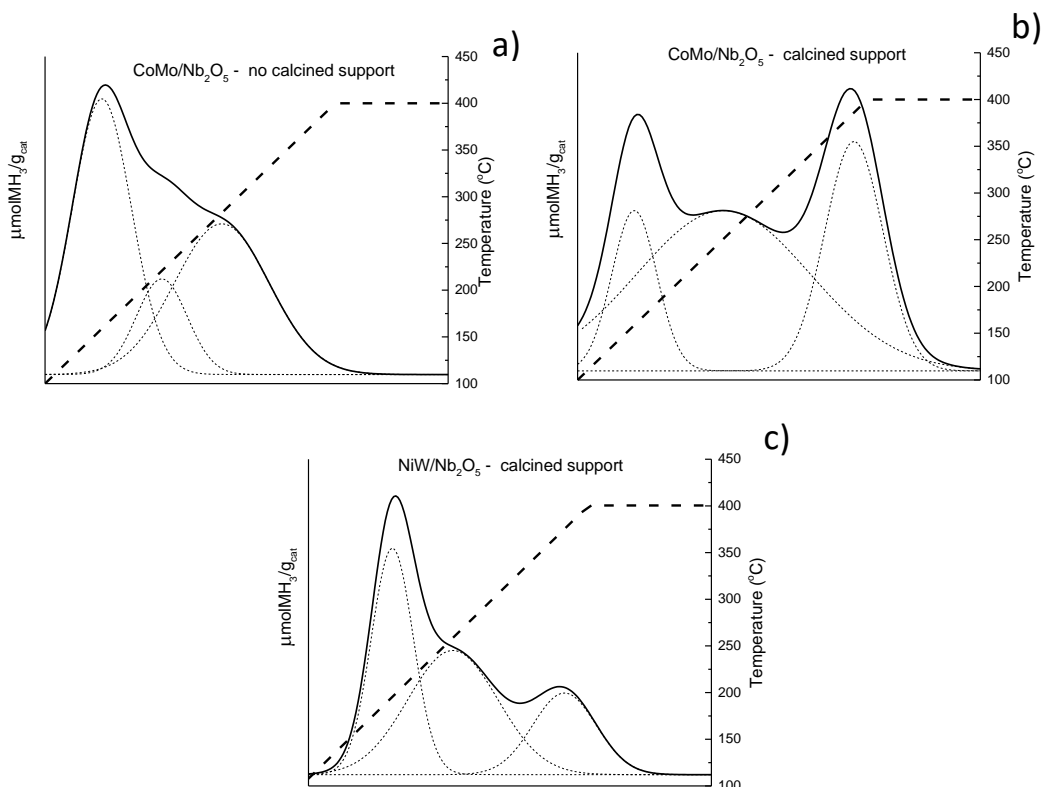


Fonte: Authors.

### 3.2. Transformation of 3-methylthiophene

The performance of these materials was compared for the transformation of 3-methylthiophene (3MT), used as model molecule representative of sulfur compounds present in FCC gasoline, under the following operating conditions: T = 250°C, P = 2 MPa and ratio H<sub>2</sub>/feed = 360 NL/L. The reaction mechanism of 3MT over a CoMo/Al<sub>2</sub>O<sub>3</sub> catalyst is presented in Figure 4 (Santos et al., 2019).


**Figure 4.** Reaction scheme for the transformation of 3MT. (T = 250°C, P = 20 bar, CoMo/Al<sub>2</sub>O<sub>3</sub>, H<sub>2</sub>/feed = 360 NL/L).

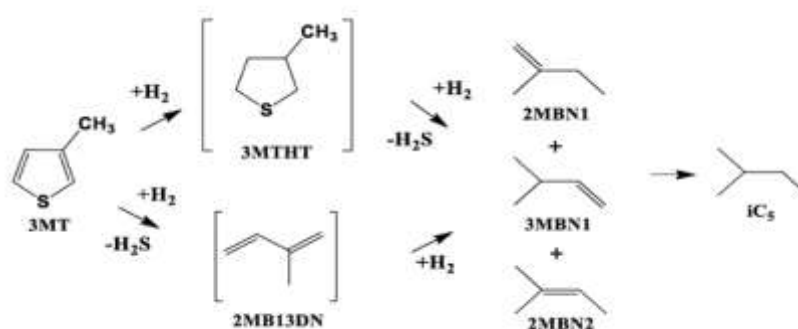

Source: Santos et al., 2019

Whatever the catalyst, the activity (measured at a conversion of about 30%) was stable during the time (Figure 5). The most active catalyst per gram and normalized per square meter was NiW/Nb<sub>2</sub>O<sub>5</sub> followed by CoMo with calcined support and CoMo with non-calcined support. The difference observed between CoMo/Nb<sub>2</sub>O<sub>5</sub> with the non-calcined and calcined support suggests an important role of the calcination step. Despite the higher specific surface area of the CoMo/Nb<sub>2</sub>O<sub>5</sub> non-calcined support catalyst, it has presented a lower catalytic activity among the three catalysts evaluated and twice as low compared with CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined support. This could be explained by the fact that increasing the calcination temperature of the niobium solid, a superficial rearrangement in the hydroxyl group occurs, and water molecules could leave the molecular structure (Santos et al., 2017). It is important to notice that even though a lower activity of the CoMo/Nb<sub>2</sub>O<sub>5</sub> non-calcined catalyst (activity for the non-calcined and calcined CoMo/Nb<sub>2</sub>O<sub>5</sub> equal to 0.12 and 0.22 mmol/g.h, respectively), the product distribution has shown a lower pentane/pentene ratio (iC<sub>5</sub>/=C<sub>5</sub>), which means a lower tendency to produce hydrogenated products during the hydrotreatment reactions (Santos et al., 2017).

**Figure 5.** 3MT transformation as function of time on stream ( $T = 250\text{ }^{\circ}\text{C}$ ,  $P = 2\text{ MPa}$ ,  $\text{H}_2/\text{feed} = 360\text{ NL/L}$ ).

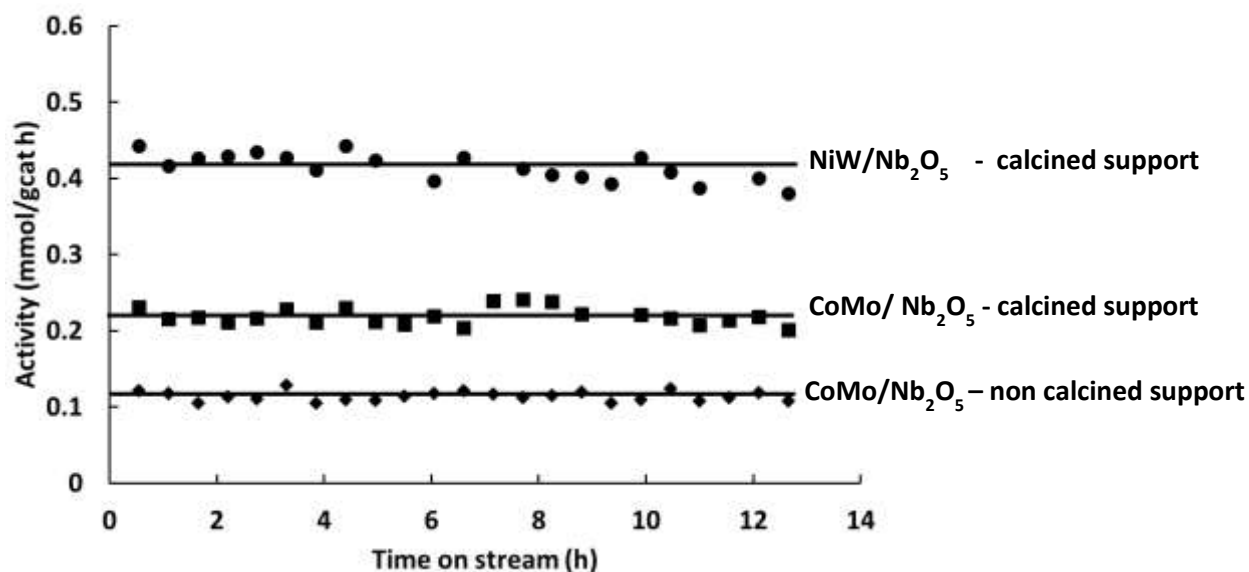

Fonte: Authors.

Furthermore, comparing the activity as well as the textural properties of the calcined  $\text{CoMo/Nb}_2\text{O}_5$  with the commercial  $\text{CoMoS/Al}_2\text{O}_3$  catalyst studied by Santos et al. (2019), it was observed that the niobium oxide has a lower efficiency as a support than alumina oxide ( $\text{Al}_2\text{O}_3$ ) according to Table 3. This difference could be attributed to the interaction metal-support as well as the lower available surface area provided by the  $\text{Nb}_2\text{O}_5$  support, which was confirmed by the comparison of BET results presented in Table 2. Indeed, the specific surface area of the alumina support is about 20 times higher in comparison with the  $\text{Nb}_2\text{O}_5$  support, which leads to a better available surface area to distribute the active phase and thus enhance the catalytic activity and selectivity. Taking into account the difference in specific surface area of alumina and niobium supports, Table 3 presents the specific catalytic activity normalized per BET surface area. Therefore, the catalytic activity of prepared  $\text{CoMo/Nb}_2\text{O}_5$  and  $\text{CoMo/Al}_2\text{O}_3$  are 0.04 and 0.05  $\text{mmol/m}^2\cdot\text{h}$ , respectively, representing a difference of about 25% higher for the commercial catalyst ( $\text{CoMo/Al}_2\text{O}_3$ ). However, when the  $\text{NiW/Nb}_2\text{O}_5$  catalyst is compared to the  $\text{CoMo/Al}_2\text{O}_3$  catalyst it is observed activities of 0.21 and 0.05  $\text{mmol/m}^2\cdot\text{h}$ , respectively which represents a factor 4 for the  $\text{NiW/Nb}_2\text{O}_5$  catalyst.

The effect of the metal-promoter interaction in the catalytic activity is evidenced through the results obtained in the transformation of 3MT over  $\text{NiW/Nb}_2\text{O}_5$  and  $\text{CoMo/Nb}_2\text{O}_5$  catalysts since the Ni:W and Co:Mo molar ratios are similar as indicated in Table 1. Indeed, the HDS reaction occurs over the  $\text{MoS}_2$  and  $\text{WS}_2$  catalytic phase formed during the sulfiding

process with H<sub>2</sub>S, prior to the hydrodesulfurization reaction. Comparing the activity of NiW/Nb<sub>2</sub>O<sub>5</sub> and CoMo/Nb<sub>2</sub>O<sub>5</sub> catalysts it is possible to notice an important difference which, in the first case, the activity is equal to 0.43 mmol/g.h and the second case equal to 0.22 mmol/g.h, representing 2 times higher for the NiW than CoMo catalyst. Comparing the catalytic activity as a function of specific surface area, it is possible to notice a difference about 5 times between calcined niobium supported NiW and CoMo catalysts (0.21 and 0.04 mmol/m<sup>2</sup>.h, respectively). These results suggest that the effect of Ni as a promoter of the WS<sub>2</sub> phase would favor the hydrogen transfer reactions more than the promotion of Co for the MoS<sub>2</sub>. This fact could facilitate the C-S scission through a direct desulfurization reaction and thus there is a higher activity of NiW over CoMo catalyst for the hydrodesulfurization of 3MT. These results are in line with the literature where a similar behavior was observed when was studied the effect of different tungsten catalysts for the hydrodesulfurization of thiophene (Bendezú et al., 2000; González-Cortés et al., 2014). Thus, these results suggest a more efficient Ni-W-S interaction in comparison with the Co-Mo-S interaction.

**Table 3.** Transformation of 3MT (T = 250 °C, P = 2 MPa, H<sub>2</sub>/feed = 360 NL/L). iC<sub>5</sub>: isopentane, 3MB1N: 3-methylbut-1-ene, 2MB1N: 2-methylbut-1-ene, 2MB2N: 2-methylbut-2-ene, iC<sub>5</sub>/=C<sub>5</sub>: ratio isopentane/pentenens.

Catalyst	BET (m <sup>2</sup> /g)	Activity (mmol/g.h)	Activity (mmol/ m <sup>2</sup> .h)	Molar Yield (%)				
				iC <sub>5</sub>	3MB1N	2MB1N	2MB2N	iC <sub>5</sub> /=C <sub>5</sub>
CoMo/Al <sub>2</sub> O <sub>3</sub> <sup>1</sup>	122	6.0	0.05	9.9	15.6	17.6	56.9	0.11
CoMo/Nb <sub>2</sub> O <sub>5</sub> non calcined support	29	0.12	0.004	11.9	10.3	12.3	65.5	0.13
CoMo/Nb <sub>2</sub> O <sub>5</sub> calcined support	6	0.22	0.04	19.1	4.6	14.4	61.9	0.24
NiW/Nb <sub>2</sub> O <sub>5</sub> calcined support	2	0.43	0.21	11.7	4.7	17.6	65.9	0.13

1. (Santos et al., 2019) at similar operating conditions. Fonte: Authors.



According to the results present in Figure 5, it is possible to observe that even by using the chelating agent in the preparation of the catalyst CoMo/Nb<sub>2</sub>O<sub>5</sub> and NiW/Nb<sub>2</sub>O<sub>5</sub>, it did not seem to be effective an increasing absolute of the catalytic activity above the catalytic activity obtained by a commercial CoMo/Al<sub>2</sub>O<sub>3</sub> catalyst. However, by comparing the catalytic activity normalized by the specific surface area, the calcined catalysts prepared by using the chelating agent have shown a similar or even higher activity when compared with the commercial CoMo/Al<sub>2</sub>O<sub>3</sub> catalyst.

#### 4. Conclusion

The transformation of 3-methylthiophene over CoMo and NiW supported on Nb<sub>2</sub>O<sub>5</sub> catalysts, under selective HDS operating conditions, has shown relevant differences in activity and product distribution. The NiW/Nb<sub>2</sub>O<sub>5</sub> catalyst presented the highest activity followed by CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined support and finally the CoMo/Nb<sub>2</sub>O<sub>5</sub> non-calcined support. However, a lower pentane/pentene ratio for the CoMo/Nb<sub>2</sub>O<sub>5</sub> non-calcined support compared with CoMo/Nb<sub>2</sub>O<sub>5</sub> calcined support suggests a tendency to produce a fewer hydrogenated product in a hydrotreatment process.

In the present study, it was possible to analyze the role of niobium as a support for hydrotreatment catalysts as well as its performance in the HDS of 3-methylthiophene. The catalysts analyzed have presented promising results either by its specific activity normalized per total BET (0.04 and 0.21 mmol/g.m<sup>2</sup> for the calcined CoMo/Nb<sub>2</sub>O<sub>5</sub> and NiW/Nb<sub>2</sub>O<sub>5</sub>) or its HDS product distribution (iC<sub>5</sub>=C<sub>5</sub> ratio = 0.13 for the non calcined CoMo/Nb<sub>2</sub>O<sub>5</sub> catalyst), which could lead to a low production of hydrogenated products in a hydrotreatment process.

In order to deeply understand the impact of different interactions metal-promoter as well as metal-support, future works could involve the same approach used in this study with different model sulfur species present in FCC gasoline. In this evaluation, the interaction between the different sulfur species and the catalytic active phase could be evaluated. Furthermore, a theoretical kinetic approach could also be investigated in order to understand the different reaction mechanisms involved.

#### Acknowledgments

This study was financed in part by the Coordenação de Aperfeiçoamento de Pessoal de

Nível Superior – Brasil (CAPES) Finance Code 001. Roberta Lopes thanks CAPES-Brasil for the Master grant as well as the University of Poitiers (IC2MP) for the opportunity to carry out the experiments and the fruitful discussions about the results. The authors acknowledge the financial support provided by Programa de Recursos Humanos da Agência Nacional do Petróleo, Gás Natural e Biocombustíveis – PRH-ANP.

## References

Aray, Y., Zambrano, D., Cornejo, M. H., Ludeña, E. V., Iza, P., Vidal, A. B., Coll, D. S., Jiménez, D. M., Henriquez, F., & Paredes, C. (2014). First-principles study of the nature of niobium sulfide catalyst for hydrodesulfurization in hydrotreating conditions. *Journal of Physical Chemistry C*, 118(48), 27823–27832. <https://doi.org/10.1021/jp5059269>

Bendezú, S., Cid, R., Fierro, J. L. G., & Agudo, A. L. (2000). Thiophene hydrodesulfurization on sulfided Ni, W and NiW / USY zeolite catalysts: effect of the preparation method. *Applied Catalysis A: General*, 197, 47–60.

Castillo-villalón, P., Ramirez, J., & Vargas-luciano, J. A. (2014). Analysis of the role of citric acid in the preparation of highly active HDS catalysts. *Journal of Catalysis*, 320, 127–136. <https://doi.org/10.1016/j.jcat.2014.09.021>

Daudin, A., Brunet, S., Perot, G., Raybaud, P., & Bouchy, C. (2007). Transformation of a model FCC gasoline olefin over transition monometallic sulfide catalysts. *Journal of Catalysis*, 248(1), 111–119. <https://doi.org/10.1016/j.jcat.2007.03.009>

Falk, G. S., Borlaf, M., Novaes de Oliveira, A. P., Rodrigues Neto, J. B., Moreno, R., & Hotza, D. (2014). Síntese e caracterização de Nb<sub>2</sub>O<sub>5</sub> por rota coloidal. *Congresso Brasileiro de Engenharia e Ciências Dos Materiais*, 1, 2665–2672. <https://doi.org/10.2466/pr0.1981.48.1.335>

Faro, A. C., Carlota, A., & Santos, B. (2006). Cumene hydrocracking and thiophene HDS on niobia-supported Ni, Mo and Ni-Mo catalysts. *Catalysis Today*, 118, 402–409. <https://doi.org/10.1016/j.cattod.2006.07.027>

Gaborit, V., Allali, N., Geantet, C., Breysse, M., Vrinat, M., & Danot, M. (2000). Niobium sulfide as a dopant for hydrotreating NiMo catalysts. *Catalysis Today*, 57(3–4), 267–273. [https://doi.org/10.1016/S0920-5861\(99\)00336-3](https://doi.org/10.1016/S0920-5861(99)00336-3)

Gonzalez-Cortes, S. L., Qian, Y., Almegren, H. A., Xiao, T., Uznetsov, V. L., & Edwards, P. P. (2014). Citric acid-assisted synthesis of  $\gamma$ -alumina-supported high loading CoMo sulfide catalysts for the hydrodesulfurization (HDS) and hydrodenitrogenation (HDN) reactions. *Applied Petrochemical Research*, 5, 181–197.

González-Cortés, S. L., Rugmini, S., Xiao, T., Green, M. L. H., Rodulfo-Baechler, S. M., & Imbert, F. E. (2014). Deep hydrotreating of different feedstocks over a highly active Al<sub>2</sub>O<sub>3</sub>-supported NiMoW sulfide catalyst. *Applied Catalysis A: General*, 475, 270–281. <https://doi.org/10.1016/j.apcata.2014.01.045>

Gutierrez, A., Turpeinen, E. M., Viljava, T. R., & Krause, O. (2017). Hydrodeoxygenation of model compounds on sulfided CoMo/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> and NiMo/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalysts; Role of sulfur-containing groups in reaction networks. *Catalysis Today*, 285, 125–134. <https://doi.org/10.1016/j.cattod.2017.02.003>

Haandel, L. Van, Bremmer, G. M., Hensen, E. J. M., & Weber, T. (2017). The effect of organic additives and phosphoric acid on sulfidation and activity of (Co)Mo / Al<sub>2</sub>O<sub>3</sub> hydrodesulfurization catalysts. *Journal of Catalysis*, 351, 95–106. <https://doi.org/10.1016/j.jcat.2017.04.012>

Huirache-Acuña, R., Pawelec, B., Loricera, C. V., Rivera-Muñoz, E. M., Nava, R., Torres, B., & Fierro, J. L. G. (2012). Comparison of the morphology and HDS activity of ternary Ni(Co)-Mo-W catalysts supported on Al-HMS and Al-SBA-16 substrates. *Applied Catalysis B: Environmental*, 125, 473–485. <https://doi.org/10.1016/j.apcatb.2012.05.034>

Kaluza, L., Gulkova, D., Zdraž, M., & Vít, Z. (2012). CoMo / ZrO<sub>2</sub> Hydrodesulfurization Catalysts Prepared by Chelating Agent Assisted Spreading. *Catalysis Letters*, 142, 969–974. <https://doi.org/10.1007/s10562-012-0857-6>

Kaluza, L., & Zdražil, M. (2018). Relative activity of Niobia-supported CoMo

hydrodesulphurization catalyst prepared with NTA: A kinetic approach. *Catalysis Communications*, 107(October 2017), 62–67. <https://doi.org/10.1016/j.catcom.2018.01.020>

Kitano, T., Shishido, T., Teramura, K., & Tanaka, T. (2012). Brønsted Acid Property of Alumina-Supported Niobium Oxide Calcined at High Temperatures: Characterization by Acid-Catalyzed Reactions and Spectroscopic Methods. *The Journal of Physical Chemistry C*, 116, 11615–11625.

Lamic, A. F., Daudin, A., Brunet, S., Legens, C., Bouchy, C., & Devers, E. (2008). Effect of H<sub>2</sub>S partial pressure on the transformation of a model FCC gasoline olefin over unsupported molybdenum sulfide-based catalysts. *Applied Catalysis A: General*, 344(1–2), 198–204. <https://doi.org/10.1016/j.apcata.2008.04.023>

Lélias, M. A., Guludec, E. Le, Mariey, L., Gestel, J. Van, Travert, A., Oliviero, L., & Mauge, F. (2010). Effect of EDTA addition on the structure and activity of the active phase of cobalt – molybdenum sulfide hydrotreatment catalysts. *Catalysis Today*, 150, 179–185. <https://doi.org/10.1016/j.cattod.2009.07.107>

León, J. N. D. De, Zavala-Sánchez, L. A., Suárez-Toriello, V. A., Alonso-Núñez, G., Zepeda, T. A., Yocupicio, R. I., Reyes, J. A. D. L., & Fuentes, S. (2017). Support effects of NiW catalysts for highly selective sulfur removal from light hydrocarbons. *Applied Catalysis B, Environmental*, 213, 167–176. <https://doi.org/10.1016/j.apcatb.2017.05.014>

Lu, X., Zhang, S., Xing, J., Wang, Y., Chen, W., Ding, D., Wu, Y., Wang, S., Duan, L., & Hao, J. (2020). Progress of Air Pollution Control in China and Its Challenges and Opportunities in the Ecological Civilization Era. *Engineering*, xxx. <https://doi.org/10.1016/j.eng.2020.03.014>

Méndez, F. J., Franco-López, O. E., Bokhimi, X., Solís-Casados, D. A., Escobar-Alarcón, L., & Klimova, T. E. (2017). Dibenzothiophene hydrodesulfurization with NiMo and CoMo catalysts supported on niobium-modified MCM-41. *Applied Catalysis B: Environmental*, 219, 479–491. <https://doi.org/10.1016/j.apcatb.2017.07.079>

Naboulsi, I., Lebeau, B., Linares, F. C., Brunet, S., Mallet, M., Michelin, L., Bonne, M.,

Carteret, C., & Blin, J.-L. (2018). Selective direct desulfurization way (DDS) with CoMoS supported over mesostructured titania for the deep hydrodesulfurization of 4,6-dimethyldibenzothiophene. *Applied Catalysis A, General*, 563, 91–97. <https://doi.org/10.1016/j.apcata.2018.06.033>

Pelardy, F., Daudin, A., Devers, E., Dupont, C., Raybaud, P., & Brunet, S. (2016). Deep HDS of FCC gasoline over alumina supported CoMoS catalyst: Inhibiting effects of carbon monoxide and water. *Applied Catalysis B: Environmental*, 183, 317–327. <https://doi.org/10.1016/j.apcatb.2015.10.026>

Pelardy, F., Silva, A., Daudin, A., Devers, E., Belin, T., & Brunet, S. (2017). Sensitivity of supported MoS<sub>2</sub>-based catalysts to carbon monoxide for selective HDS of FCC gasoline: Effect of nickel or cobalt as promoter. *Applied Catalysis B, Environmental*, 206, 24–34. <https://doi.org/10.1016/j.apcatb.2016.12.057>

Pereira, A. S., Shitsuka, D. M., Parreira, F. J., & Shitsuka, R. (2018). *Metodologia da Pesquisa Científica*.

Pereyma, V. Y., Klimov, O. V., Prosvirin, I. P., Gerasimov, E. Y., Yashnik, S. A., & Noskov, A. S. (2018). Effect of thermal treatment on morphology and catalytic performance of NiW / Al<sub>2</sub>O<sub>3</sub> catalysts prepared using citric acid as chelating agent. *Catalysis Today*, 305(April 2017), 162–170. <https://doi.org/10.1016/j.cattod.2017.07.019>

Salazar, N., Beinik, I., & Lauritsen, J. V. (2017). Single-layer MoS<sub>2</sub> formation by sulfidation of molybdenum oxides in different oxidation states on Au(111). *Royal Society of Chemistry*, 19, 14020.

Santos, D. P. B., Silva, C. T., & Albuquerque, R. V. T. de. (2017). Preparação e Caracterização do Óxido de Nióbio obtido a partir do Ácido Nióbico (Nb<sub>2</sub>O<sub>5</sub>nH<sub>2</sub>O) por Decomposição Térmica Direta. *Exatas Online*, 8(2), 1–8. <https://doi.org/10.1016/j.pmatsci.2016.02.001>

Santos, A. S. dos. (2017). *Transformation de composés modèles soufres et oléfiniques représentatifs d'une essence de fcc – approche expérimentale et théorique*. Université de Poitiers.

Santos, A. S. dos, Brunet, S., Girard, E., & Leflaive, P. (2019). Competitive adsorptions between thiophenic compounds over a CoMoS/Al<sub>2</sub>O<sub>3</sub> catalyst under deep HDS of FCC gasoline. *Applied Catalysis A : General*, 570(25), 292–298.

Silva, J. I. S., & Secchi, A. R. (2018). An approach to optimize costs during ultra-low hydrodesulfurization of a blend consisting of different oil streams. *Brazilian Journal of Chemical Engineering*, 35(4), 1293–1304. <https://doi.org/10.1590/0104-6632.20180354s20170370>

Silva, M. L. C. P., Silva, G. L. J. P., & Tagliaferro, G. V. (2000). Obtenção e caracterização do óxido de nióbio 9(V) hidratado por precipitação em solução homogênea. *Congresso Brasileiro de Engenharia e Ciência Dos Materiais*, 14(9), 1689–1699. <https://doi.org/10.1017/CBO9781107415324.004>

Valencia, D., & Klimova, T. (2012). Kinetic study of NiMo / SBA-15 catalysts prepared with citric acid in hydrodesulfurization of dibenzothiophene. *Catalysis Communications*, 21, 77–81. <https://doi.org/10.1016/j.catcom.2012.02.003>

Valencia, D., Klimova, T., & Pena, L. (2014). CoMo / SBA-15 catalysts prepared with EDTA and citric acid and their performance in hydrodesulfurization of dibenzothiophene. *Applied Catalysis B : Environmental*, 147, 879–887. <https://doi.org/10.1016/j.apcatb.2013.10.019>

**Percentage of contribution of each author in the manuscript**

Roberta Lopes do Rosário – 30%

Ronaldo Costa Santos – 14%

Alan Silva dos Santos – 14%

Alexandre Carvalho – 14%

Sylvette Brunet – 14%

Luiz Antônio Magalhães Pontes – 14%