



HAL
open science

Enhancing the Activity and Stability of Carbon-Supported Platinum-Gadolinium Nanoalloys towards the Oxygen Reduction Reaction

Carlos Augusto Campos Roldán, Frédéric Pailloux, Pierre-Yves Blanchard,
Deborah Jones, Jacques Rozière, Sara Cavaliere

► **To cite this version:**

Carlos Augusto Campos Roldán, Frédéric Pailloux, Pierre-Yves Blanchard, Deborah Jones, Jacques Rozière, et al. Enhancing the Activity and Stability of Carbon-Supported Platinum-Gadolinium Nanoalloys towards the Oxygen Reduction Reaction. *Nanoscale Advances*, 2022, 4, pp.26 - 29. 10.1039/D1NA00740H . hal-03432743

HAL Id: hal-03432743

<https://hal.science/hal-03432743>

Submitted on 17 Nov 2021

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Nanoscale Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: C. A. A. Campos Roldán, F. Pailloux, P. Blanchard, D. J. Jones, J. Rozière and S. Cavaliere, *Nanoscale Adv.*, 2021, DOI: 10.1039/D1NA00740H.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

COMMUNICATION

Enhancing the Activity and Stability of Carbon-Supported Platinum-Gadolinium Nanoalloys towards the Oxygen Reduction Reaction

C.A. Campos-Roldán,^a F. Pailloux,^b P.Y. Blanchard,^a D. J. Jones,^a J. Rozière,^a and S. Cavaliere,^{*a,c}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

The activity/stability towards the ORR of Pt_xGd/C nanoalloys has been enhanced by controlling the atmosphere during the dealloying process. By minimising the formation of porous nanoarchitectures, the ORR activity is increased, and is accompanied by higher activity retention and attenuation of metal dissolution on cycling to high voltage.

Platinum-rare earth metal (Pt-REM) alloys have been reported as being some of the most active and stable electrocatalysts towards the oxygen reduction reaction (ORR), in particular the Pt-Gd system.^{1, 2} From previous studies on Pt-Gd sputter-cleaned polycrystalline surfaces^{1, 3} and non-supported nanoparticles (NPs)² it can be concluded that the ORR enhancement is related to the formation of a strained Pt overlayer due to the lattice contraction caused by the Pt-Gd alloy core,⁴ that weakens the binding energy between Pt and oxygen. Moreover, their long-term stability towards the ORR was linked to the Pt-Gd alloy formation energy, as well as the protective Pt overlayer.¹ However, the desirable production of actual Pt-Gd NPs dispersed over high surface-area supports is the bottleneck for the implementation of these systems in proton exchange membrane fuel cell (PEMFC) technologies,^{5–8} since the reduction potential of Gd is far beyond the stability range of water.⁹ Thus, the Pt-Gd nanoalloy formation represents a big challenge. Recently, Hu et al.⁹ have developed a solid-state synthesis approach to produce carbon-supported Pt-REM nanostructures directly. Taking the Pt-Gd/C system as model,¹⁰ the authors have reported a high active ORR electrocatalyst; however, its stability did not match the expected behaviour. This feature is related to the crystalline phase (cubic Pt₂Gd) and the formation of porous nanoarchitectures which are

easily degraded under the harsh ORR conditions (nanoalloy segregation, metal dissolution, morphology transitions, etc),¹¹ resulting in significant performance decay. The formation of such sponge-like structures has been also reported for nanoparticulate systems such as Pt-Ni¹² and Pt-Co¹³, where they compromise the activity/stability benefits of the alloyed systems. Therefore, the stability enhancement of the novel nanostructured Pt-Gd/C system is of paramount importance for its implementation in PEMFC. Herein, we have produced Pt_xGd/C nanostructures using a solid-state synthesis method and provide evidence that the formation of the porous structures is minimised (but not suppressed) through a N₂-atmosphere dealloying process, leading to ORR activity/stability enhancement.

Following our previous contribution,¹¹ in which we have identified the optimal Pt:Gd composition, Pt_xGd NPs dispersed over conventional carbon Vulcan XC-72 were prepared. After the synthesis reaction (see details in the SI†), the XRD pattern of the as-prepared material, Fig. S1†, shows the Pt₂Gd and Pt₃Gd reflections, along with GdO_x and cyanamide crystalline complexes. Such reaction sub-products might be removed via an acidic wash.¹⁰ Simultaneously, the dealloying process, i.e. the selective dissolution of Gd, takes place, leading to the formation of a Pt shell around the Pt_xGd alloy core. The gaseous environment in which the dealloy protocol is performed has a great impact on the free corrosion potential (or open circuit potential, OCP) of a corroding system:¹⁴ the presence of oxygen creates a complex mixed OCP, which affects the dealloying kinetics.¹⁴ With this knowledge, we have produced and compared the electrocatalysts obtained by the acid wash under air- vs. N₂-atmosphere (see detail in the SI†). Fig. 1 reveals that the remaining sub-products are successfully removed after both leaching protocols, confirming the formation of Pt-Gd alloy (Pt₂Gd and Pt₃Gd reflections). The XPS spectra, cf. Fig. 1b, support formation of the Pt-Gd alloy with features characteristic of the metallic states of both elements.² Besides, the binding energy of the Pt signals is downshifted with respect to the Pt/C reference material, suggesting a modification of the Pt electronic structure.^{15, 16}

^a ICGM, Université de Montpellier, CNRS, ENSCM, 34095 Montpellier cedex 5, France.

^b Institut P', CNRS-Université de Poitiers-ISA-ENSMA-UPR 3346, 11 Boulevard Marie et Pierre Curie, Site du Futuroscope, TSA 41123, 86073 Poitiers cedex 9, France.

^c Institut Universitaire de France (IUF), 1 rue Descartes 75231 Paris cedex 05, France.

†Electronic Supplementary Information (ESI) available: Experimental details, materials synthesis and characterisation, and complementary XRD, TEM, STEM and electrochemical results are included. See DOI: 10.1039/x0xx00000x



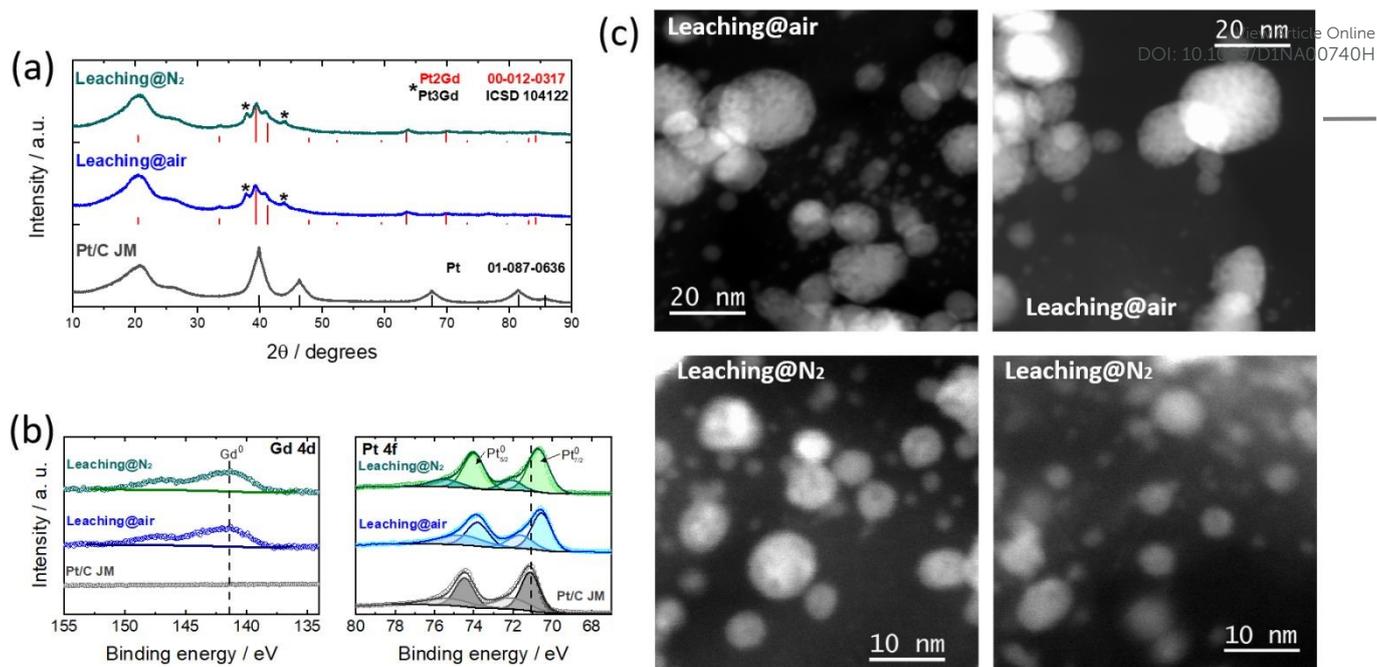


Fig. 1 (a) Powder XRD patterns; (b) Gd 4d and Pt 4f photoemission lines; and (c) high-angle annular dark field STEM micrographs of the Pt_xGd/C catalysts washed under air- or N₂-atmosphere. 40% Pt/C from Johnson-Matthey is used as reference in (a) and (b).

The metal content and Pt:Gd ratio, in the bulk and at the near-surface level, were estimated using ICP-MS and XPS, Table 1, and a slightly higher Pt:Gd ratio was observed after the leaching under N₂-atmosphere. Moreover, the TEM micrographs shown in Fig. S2[†] reveal that, regardless of the leaching treatment, a bimodal particle size distribution is observed, mean values of which have the same magnitude (Table 1). The STEM micrographs depicted in Fig. 1c, however, show that porous nanoarchitectures are formed through the leaching under air atmosphere. We have reported that the nanopore formation initiates where Gd is relatively abundant in the particle,¹¹ and its dissolution can proceed until Pt is sufficiently available to form a protective layer and stabilise the structure. This effect is pronounced in NPs with sizes > 10 nm.¹¹ Although the population of these structures is attenuated with the wash under N₂-atmosphere, in some regions we have observed porous NPs (Fig. S3[†]). Therefore, the acid wash under N₂-atmosphere substantially modulates (but does not impede) the formation of porous NPs. Gan et al.¹⁴ have demonstrated that for dealloyed PtNi₃ NPs, the absence of oxygen decreases the dissolution rate of the less noble metal; thus, the Pt surface diffusion is fast enough to stabilise the structure and prevent the formation of nanoporosity.

Table 1. Chemical composition and mean particle size of the Pt_xGd/C catalysts dealloyed under air- or N₂-atmosphere.

Sample	Metal content (% wt.)	Pt:Gd ratio (ICP-MS)	Pt:Gd ratio (XPS)	Mean particle size (nm)
Leaching@air	Pt: 27.2	Pt _{4.7} Gd	Pt _{8.3} Gd	7.8 ± 1.2
	Gd: 4.2			14.1 ± 2.6
Leaching@N ₂	Pt: 26.5	Pt _{4.5} Gd	Pt _{7.8} Gd	7.6 ± 1.4
	Gd: 4.6			14.9 ± 2.8

On the other hand, DFT screenings have suggested that the presence of oxygen induces non-precious metal surface segregation in Pt-based alloys.¹⁷ Our results reflect such an effect.

The surface electrochemistry was examined in 0.1 M HClO₄ at the beginning of the accelerated degradation test (BoT), cf. Fig. 2a and Fig. S4[†], when the typical Pt signals in acid electrolyte were acquired. The H_{upd} region of the Pt_xGd/C materials present different shapes with respect to Pt/C. This observation supports the change in the Pt-H interactions coming from the alloying effect.¹⁸ While such Pt signals seem to be unaltered at the end of the test (EoT) for the Pt_xGd/C materials, the voltammogram of Pt/C shows that this catalyst underwent evident degradation (Fig. S4[†]).

The ECSA values were determined by the CO-stripping method (Fig. S5[†]). One can notice that, for both Pt_xGd/C materials at the BoT and EoT, there are two CO-oxidation processes, which are related to the mix of agglomerated particles and small NPs.¹⁹ The TEM analysis shown in Fig. S2 supports this argument. Moreover, the relationship between the integrated charge (Q) for the H_{upd} desorption and the CO-stripping process has been considered as an indicator for the surface structural and electronic properties.¹⁸ Table 2 reports this parameter for the electrocatalysts under comparison. For Pt/C, the Q_{CO}/2Q_{Hupd} is close to 1, in concordance with previous studies.¹⁸ In the case of both Pt_xGd/C materials, the higher Q_{CO} value with respect to 2Q_{Hupd} indicates the well-known changed adsorption properties for Pt alloys.^{3, 18}



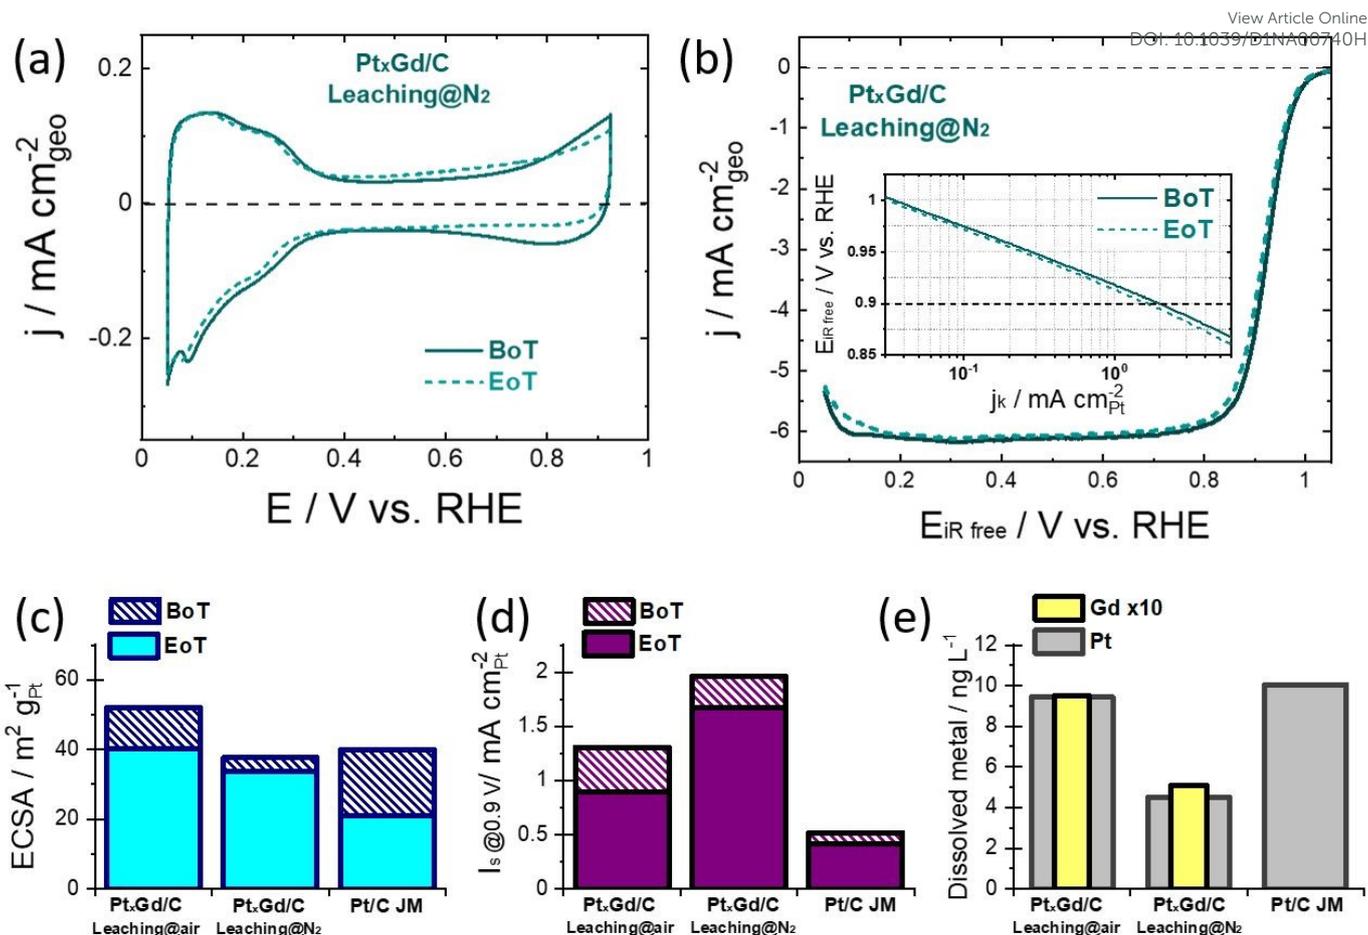


Fig. 2 (a) Cyclic voltammograms (N_2 -saturated 0.1 M HClO_4 at 20 mV s^{-1}); (b) ORR polarisation curves (O_2 -saturated 0.1 M HClO_4 at 20 mV s^{-1} and 1600 rpm) at BoT and EoT (the insert shows the iR -free electrode potential vs. mass-corrected kinetic current normalized by Pt surface); (c) ECSA values at BoT and EoT; (d) specific activity at 0.9 V at BoT and EoT; and (e) dissolved Pt and Gd in the electrolyte of the $\text{Pt}_x\text{Gd}/\text{C}$ catalysts washed under air- or N_2 -atmosphere. 40% Pt/C from Johnson-Matthey is used as reference in (c)-(e).

Besides, the $Q_{\text{CO}}/2Q_{\text{Hupd}}$ values for both $\text{Pt}_x\text{Gd}/\text{C}$ materials suggest the formation of the Pt-skeleton structure ($0.94 < Q_{\text{CO}}/2Q_{\text{Hupd}} < 1.5$),²⁰ which is maintained at the EoT. We have previously reported the formation of the Pt overlayer in this system, which supports this observation.¹¹

Notably, the ORR polarisation curves reveal a higher activity retention of the $\text{Pt}_x\text{Gd}/\text{C}$ acid-washed under N_2 -atmosphere, cf. Fig. 2b and Fig. S4†. The ECSA and specific-surface activity, at the BoT and at EoT, are shown in Fig. 2c-d. The Pt and Gd dissolution occurring during the degradation protocol was estimated by ex situ ICP-MS measurements of the electrolyte at the EoT, cf. Fig. 2d. Such kinetic parameters are shown in Table 2. In terms of ECSA, the higher value of the air-leached material reflects the higher population of porous nanoarchitectures which, at the EoT, experience a considerable degradation as confirmed by the higher concentration of Gd dissolved into the electrolyte at EoT.

This undesirable degradation is suppressed in the solid NPs produced by the N_2 -atmosphere leaching. In terms of the ORR intrinsic activity, i.e., the specific activity I_s evaluated at 0.9 V, both $\text{Pt}_x\text{Gd}/\text{C}$ electrocatalysts outperform the reference Pt/C material. However, the N_2 -leached material is characterised by a higher I_s , demonstrating that the solid NPs present higher intrinsic activity. Such an effect could be related to the higher Gd concentration at the near-surface region, which induces a stronger strain/ligand effects on the Pt overlayer, boosting the ORR kinetics.

At the EoT, the N_2 -leached $\text{Pt}_x\text{Gd}/\text{C}$ retained ca. 85% of its initial I_s , whereas the air-leached $\text{Pt}_x\text{Gd}/\text{C}$ retained ca. 67%. The higher Gd dissolution could weaken the strain/ligand effect for the air-leached $\text{Pt}_x\text{Gd}/\text{C}$; thus, the solid NPs confer higher intrinsic ORR activity and stability.



COMMUNICATION

Table 2. ORR kinetic parameters of the Pt_xGd/C catalysts leached under air- or N₂-atmosphere (*at EoT).

Sample	Q _{CO} /2Q _{Hupd}	ECSA _{CO} (m ² g _{Pt} ⁻¹)	I _{s@0.9V} (mA cm ⁻² _{Pt})	I _{m@0.9V} (A mg ⁻¹ _{Pt})	Dissolved Pt (ng L ⁻¹)	Dissolved Gd (ng L ⁻¹)
Leaching@air	1.09	52.01	1.31	0.68		
	1.06*	40.18*	0.89*	0.36*	9.45*	95.24*
	1.12	37.70	1.96	0.72		
Leaching@N ₂	1.10*	33.75*	1.67*	0.59*	4.51*	50.07*

Conclusions

The activity/stability of carbon-supported Pt_xGd nanoalloys has been improved by minimising the formation of porous nanoarchitectures. This feature was achieved by performing the dealloying process under N₂-atmosphere in order to avoid the O₂-induced Gd segregation, and favour the stabilisation of solid NPs. Such NPs present higher intrinsic ORR activity and, more important, a notably higher stability. The results in this work might be a baseline to produce high active/stable Pt-REM/C nanoalloys.

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript. C.A. Campos-Roldán, Investigation, Methodology, Data curation, Writing - original draft. F. Pailloux HAADF-STEM experiments, Writing - review & editing D. J. Jones, Funding acquisition, Conceptualization, Writing - review & editing P.-Y. Blanchard, Supervision, Writing - review & editing J. Rozière, Conceptualization, Writing - review & editing S. Cavaliere, Funding acquisition, Conceptualization, Supervision, Writing - review & editing.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The research leading to these results has received funding from the European Research Council under the European Union's Seventh Framework Programme/ERC Grant Agreement SPINAM no. 306682 and from the European Union's Horizon 2020 research and innovation programme, Fuel Cells and Hydrogen 2 Joint Undertaking under the GAIA project, Grant Agreement No 826097. This Joint Undertaking receives support from the European Union's Horizon 2020 research and innovation programme, Hydrogen Europe and

Hydrogen Europe Research. SC acknowledges IUF for financial support.

References

- M. Escudero-Escribano, A. Verdager-Casadevall, P. Malacrida, U. Gronbjerg, B. P. Knudsen, A. K. Jepsen, J. Rossmeisl, I. E. Stephens and I. Chorkendorff, *J Am Chem Soc*, 2012, **134**, 16476-16479.
- A. Velázquez-Palenzuela, F. Masini, A. F. Pedersen, M. Escudero-Escribano, D. Deiana, P. Malacrida, T. W. Hansen, D. Friebe, A. Nilsson, I. E. L. Stephens and I. Chorkendorff, *J. Catal.*, 2015, **328**, 297-307.
- M. Escudero-Escribano, P. Malacrida, M. Hansen, U. Vej-Hansen, A. Velázquez-Palenzuela, V. Tripkovic, J. Schiøtz, J. Rossmeisl, I. Stephens and I. Chorkendorff, *Science*, 2018, **352**, 73-76.
- A. F. Pedersen, E. T. Ulrikkeholm, M. Escudero-Escribano, T. P. Johansson, P. Malacrida, C. M. Pedersen, M. H. Hansen, K. D. Jensen, J. Rossmeisl, D. Friebe, A. Nilsson, I. Chorkendorff and I. E. L. Stephens, *Nano Energy*, 2016, **29**, 249-260.
- J. N. Schwämmlein, G. S. Harzer, P. Pfändner, A. Blankenship, H. A. El-Sayed and H. A. Gasteiger, *J Electrochem Soc*, 2018, **165**, J3173-J3185.
- S. G. Peera, T. G. Lee and A. K. Sahu, *Sustain. Energ. Fuels*, 2019, **3**, 1866-1891.
- T. Chu, M. Xie, D. Yang, P. Ming, B. Li and C. Zhang, *International Journal of Hydrogen Energy*, 2020, **45**, 27291-27298.
- B. Eriksson, G. Montserrat-Sisó, R. Brown, T. Skála, R. Wreland Lindström, G. Lindbergh, B. Wickman and C. Lagergren, *Electrochimica Acta*, 2021, **387**, 138454.
- Y. Hu, J. O. Jensen, L. N. Cleemann, B. A. Brandes and Q. Li, *J Am Chem Soc*, 2020, **142**, 953-961.
- Y. Hu, J. O. Jensen, P. Norby, L. N. Cleemann, F. Yang and Q. Li, *Chemistry of Materials*, 2021, **33**, 535-546.
- C. A. Campos-Roldán, F. Pailloux, P.-Y. Blanchard, D. J. Jones, J. Rozière and S. Cavaliere, *ACS Catalysis*, 2021, DOI: 10.1021/acscatal.1c02449, 13519-13529.
- C. Baldizzone, L. Gan, N. Hodnik, G. P. Keeley, A. Kostka, M. Heggen, P. Strasser and K. J. J. Mayrhofer, *ACS Catalysis*, 2015, **5**, 5000-5007.



Journal Name

COMMUNICATION

13. A. K. Schuppert, A. Savan, A. Ludwig and K. J. J. Mayrhofer, *Electrochimica Acta*, 2014, **144**, 332-340.
14. L. Gan, M. Heggen, R. O'Malley, B. Theobald and P. Strasser, *Nano Letters*, 2013, **13**, 1131-1138.
15. C. A. Campos-Roldán, G. Ramos-Sanchez, R. G. Gonzalez-Huerta, J. R. Vargas Garcia, P. B. Balbuena and N. Alonso-Vante, *ACS Appl Mater Interfaces*, 2016, **8**, 23260-23269.
16. S. J. Hwang, S. K. Kim, J. G. Lee, S. C. Lee, J. H. Jang, P. Kim, T. H. Lim, Y. E. Sung and S. J. Yoo, *J Am Chem Soc*, 2012, **134**, 19508-19511.
17. M. Sarwar, J. L. Gavartin, A. Martinez Bonastre, S. Garcia Lopez, D. Thompsett, S. C. Ball, A. Krzystala, G. Goldbeck and S. A. French, *Phys Chem Chem Phys*, 2020, **22**, 5902-5914.
18. D. F. van der Vliet, C. Wang, D. Li, A. P. Paulikas, J. Greeley, R. B. Rankin, D. Strmcnik, D. Tripkovic, N. M. Markovic and V. R. Stamenkovic, *Angew Chem Int Ed Engl*, 2012, **51**, 3139-3142.
19. C. A. Campos-Roldán and N. Alonso-Vante, *J Solid State Electrochem*, 2021, **25**, 187-194.
20. R. Chattot, I. Martens, M. Scohy, J. Herranz, J. Drnec, F. Maillard and L. Dubau, *ACS Energy Letters*, 2019, **5**, 162-169.

View Article Online
DOI: 10.1039/D1NA00740H

Open Access Article. Published on 15 November 2021. Downloaded on 11/17/2021 12:46:39 PM.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



Nanoscale Advances Accepted Manuscript