



**HAL**  
open science

## Effect of the electron donating group on the excited-state electronic nature and epsilon-near-zero properties of curcuminoid-borondifluoride dyes

Kyu-Ri Choi, Dae Hyeon Kim, Yeon Ui Lee, Virginie Placide, Steven Huynh, Dandan Yao, Gabriel Canard, Elena Zaborova, Fabrice Mathevet, Loïc Mager, et al.

### ► To cite this version:

Kyu-Ri Choi, Dae Hyeon Kim, Yeon Ui Lee, Virginie Placide, Steven Huynh, et al.. Effect of the electron donating group on the excited-state electronic nature and epsilon-near-zero properties of curcuminoid-borondifluoride dyes. *RSC Advances*, 2021, 11 (60), pp.38247-38257. 10.1039/d1ra08025c . hal-03455928

**HAL Id: hal-03455928**

**<https://hal.science/hal-03455928>**

Submitted on 29 Nov 2021

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution - NonCommercial 4.0 International License

**Effect of the electron donating group on excited-state electronic nature and epsilon-near-zero properties of curcuminoid-borondifluoride dyes**

*Kyu-Ri Choi<sup>1</sup>, Dae Hyeon Kim<sup>1</sup>, Yeon Ui Lee<sup>2</sup>, Virginie Placide<sup>1</sup>, Steven Huynh<sup>1</sup>, Dandan Yao<sup>3</sup>, Gabriel Canard<sup>3</sup>, Elena Zaborova<sup>3</sup>, Fabrice Mathevet<sup>4,7</sup>, Loïc Mager<sup>5</sup>, Benoît Heinrich<sup>5</sup>, Jean-Charles Ribierre<sup>6</sup>, Jeong Weon Wu,<sup>1\*</sup> Frédéric Fages,<sup>3\*</sup> Anthony D'Aléo<sup>3,5\*</sup>*

<sup>1</sup> *Department of Physics, Ewha Womans University, Seoul 03760, Republic of Korea*

<sup>2</sup> *Department of Physics, Chungbuk National University, Chungbuk 28644, Republic of Korea*

<sup>3</sup> *Aix Marseille Univ, CNRS, CINaM UMR 7325, Campus de Luminy, Case 913, 13288 Marseille, France*

<sup>4</sup> *Sorbonne Universités, Faculté des Sciences, CNRS, Parisien de Chimie Moléculaire (IPCM), UMR 8232, Chimie des Polymères, 75005 Paris, France*

<sup>5</sup> *Université de Strasbourg, CNRS, Institut de Physique et Chimie des Matériaux de Strasbourg, UMR 7504, F-67000 Strasbourg, France*

<sup>6</sup> *Center for Organic Photonics and Electronics Research (OPERA), Kyushu University, Fukuoka 819-0395, Japan*

Keywords: Epsilon-near-zero, Curcuminoid, Organic thin film

## Abstract

Epsilon-near-zero (ENZ) properties have been reported in organic molecular films. In particular, cyanine and squaraine films have been shown to exhibit ENZ properties in the visible spectral region with a strong 3<sup>rd</sup> order nonlinear optical response near ENZ spectral region. Noting both cyanine and squaraine belong to the polymethine family, a series of six curcuminoid borondifluoride (Curc) derivatives were developed to examine whether such a polymethine character is positively correlated with the ENZ property of the organic films. Those Curc derivatives possess a Donor-Acceptor-Donor (D-A-D) architecture with acceptor, AcacBF<sub>2</sub>, located at the molecular center. Backbone of Curc is designed such that the donor strength can be tuned to transit between charge transfer (CT) and polymethine characters. This balance between CT and polymethine characters of the Curc series is examined based on the Lippert-Mataga plot. As donor strength in the D-A-D structure increases, CT character is less marked resulting in a more dominant polymethine character. The structural and optical properties of the Curc films with a thickness in the order of 30 nm were examined to correlate the polymethine character with the ENZ response. The results obtained in isotropic Curc thin films demonstrate that an increase of polymethine character associated with a stronger donor strength leads to an appearance/enhancement of the ENZ property in the visible spectrum range from 500 to 670 nm. Overall, this study provides useful guidelines to engineer new organic materials showing ENZ properties in a desired spectral range.

## 1. Introduction

Epsilon-near-zero (ENZ) materials, characterized by their permittivity close to zero within a certain spectral range, have recently attracted growing interest for their linear and large non-linear optical properties.[1-3] Their unique features make them indeed particularly appealing for different types of optical applications including nonlinear fast optical switching, radiation pattern tailoring or directional light emission.[4-6] Those ENZ properties have been observed in a variety of optical media. Examples include noble metals with Drude-type permittivity, hyperbolic metamaterials composed of multi-stack of metal and dielectric layers[7], hyperbolic metamaterials composed of metallic nano-rods embedded in oxide[8], oxide films[2, 9, 10], etc... In addition, a few examples of organic materials with ENZ properties have been reported by us and others [11-17], including monolithic natural hyperbolic material[11], polymethine dye[12-15], porphyrin[16] and polyaromatic octupolar molecule[17]. Such organic ENZ materials present some advantages compared to their inorganic counterparts, for instance, in terms of ease of processing and mechanical flexibility but further works are still required to establish their structure-property relationship and unlock their potential for photonic applications.


Among the organic ENZ materials previously reported in the literature [12], sodium [5,6-dichloro-2-[[5,6-dichloro-1-ethyl-3-(4-sulphobutyl)-benzimidazol-2-ylidene]-propenyl]-1-ethyl-3-(4-sulphobutyl)-benzimidazolium hydroxide] (TDBC) cyanine and [2,4-bis[8-hydroxy-1,1,7,7-tetramethyljulolidin-9-yl]squaraine] (HTJSq) are of interest, since a strong 3<sup>rd</sup> order nonlinear optical response was observed in spin-coated films near ENZ spectral range in the visible part of the spectrum. Noting that both TDBC and HTJSq belong to the class of polymethine dyes (i.e. molecule composed of odd number of carbons in the alternation of single and double bonds), it is tempting to make the correlation between the polymethine character of the molecules and their ENZ properties in films in order to find a strategy to develop new organic ENZ molecules. For this purpose, donor-acceptor-donor (D-A-D) curcuminoid borondifluoride derivatives represent excellent candidates since their polymethine character can be chemically tuned by the donor strength.[18]

In fact, this research work addresses two important issues that are particularly relevant for the future development of organic ENZ materials. First, in order to establish the structure-property relationship of donor strength and polymethine character, six new curcuminoid borondifluoride (Curc) dyes are synthesized. All the six Curc dyes contain the AcacBF<sub>2</sub> motif as strong electron withdrawing group at the center of the D-A-D structure and varied donor groups on each end, allowing to relate the donor strength with charge transfer (CT) character vs. polymethine character. Second, in order to identify the correlation between the polymethine character of the molecules and their ENZ property in film, the six Curc dyes were deposited into thin films on the order of 30 nm using spin-coating. For each of the six films, the presence of ENZ property is examined and the feature of ENZ spectral range and polymethine character of Curc dye is compared. This study allows us to clearly establish the impact of the electron

donor strength on the polymethine character in solution and the ENZ property in the solid state, providing a useful indication of the structure-property relationship in this family of curcuminoid derivatives and should be taken into account in further works devoted to the ENZ properties of organic materials.

## 2. Synthesis of curcuminoid- borondifluoride series with varied donors

A recent study has shown that curcuminoid borondifluoride can exhibit polymethine character by tuning the acceptor strength.[18] Now, to investigate the correlation between the donor strength and polymethine character, we designed and synthesized a series of curcuminoid derivatives. The D-A-D structures of those dyes were designed by keeping the acceptor strength constant (Acacetyl acetate Boron difluoride, AcacBF<sub>2</sub>) and changing the donor strength to produce six D-A-D Curc as shown in Figure 1. Therefore, this series allows to estimate the effect of donor groups on the polymethine character of Curc.

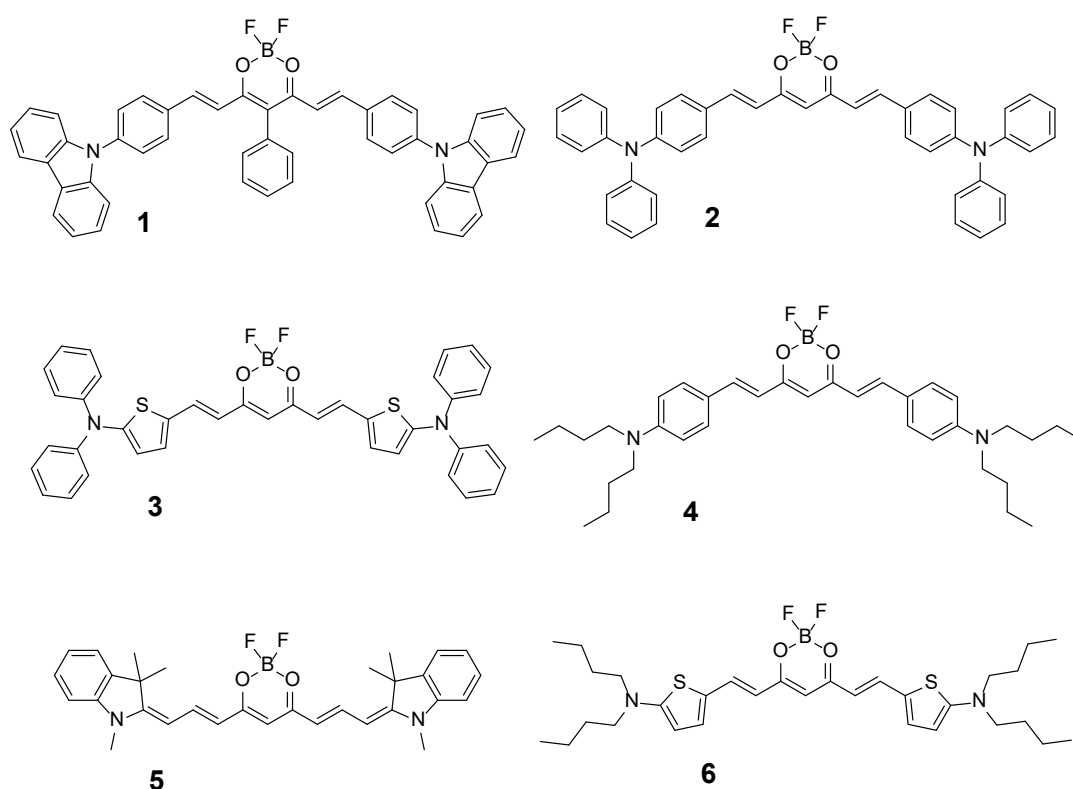

**Figure 1.** Molecular structure of compound **1**, **2**, **3**, **4**, **5**, and **6**. Compound **1** is curcuminoid – carbazol (Curc-CBz), compound **2** is Curcuminoid -triphenylamine (Curc-TPA), compound **3** is Curcuminoid-Thiophene(Curc-ThiopPh), compound **4** is Curcuminoid-dibutylAmine (Curc-PhNBu<sub>2</sub>), compound **5** is Curcuminoid-Indol (Curc-Indol), and compound **6** is Curcuminoid-Thiophene dibutylamine (Curc-ThiopBu<sub>2</sub>).

## 2.1. Electrochemistry of Curc series

Cyclic voltammetry (CV) of the six Curc series in dichloromethane solution was performed to determine oxidation and reduction waves that are centred on the end-group donor and central acceptor, respectively, as shown in Table 1 (and Figure S1). Therefore, the oxidation potential allowed to roughly rank the selected donors in this study.

**Table 1.** List of the oxidation potential (V vs. SCE), and HOMO-LUMO of six Curc series.

Compound	$E_{1/2}$ red1 (V)	$E_{1/2}$ ox1 (V)	HOMO-LUMO gap (eV)	Published
<b>1</b>	-1.10	0.92	2.02	Herein
<b>2</b>	-1.27	0.58	1.85	Ref [26]
<b>3</b>	-1.27	0.26	1.53	Herein
<b>4</b>	-1.44	0.31	1.75	Herein
<b>5</b>	-1.67	0.07	1.74	Herein
<b>6</b>	-1.49	0.02	1.51	Herein

As can be seen, the oxidation potential varies from 0.92V to 0.02V (for **1** and **6**, respectively), clearly assessing that the carbazole (in **1**) is the weakest donor and the dibutylaminothiophene (in **6**) is the strongest donor. Following those experiments, the following donor strength ranking can be assessed: **1** < **2** < **4** < **3** < **5** < **6**.

Here, it is interesting to note that the reduction potential (*i.e.*, the ability for AcacBF<sub>2</sub> to accept an electron) becomes lower as the donor strength is increased, suggesting that either the electron density increases at the location of the boron atom or the polymethine form is reached resulting in the presence of B<sup>-</sup>. Overall, those electrochemistry results show that this series of six curcuminoid derivatives is well suited to examine the effects of the donor strength on their optical and photophysical properties.

## 2.2. Photophysical properties and solvatochromism study of six Curc series


To examine the dependence of photophysical properties on the donor strength, UV/visible absorption and photoluminescence (PL) spectra of six Curc series were measured in diluted dichloromethane solution. As can be seen in Figure 2a, for UV/vis absorption spectrum, the absorption band is red-shifting

when increasing the donor strength of the dye with maxima spanning from 518 to 692 nm, respectively (for **1** and **6**, respectively). This red-shift is consistent with the donor strength, yielding **1** (518 nm) < **2** (594 nm) < **4** (619 nm) < **5** (659 nm) < **3** (665 nm) < **6** (692 nm). It is to be noted that only the compound **3** ( $\lambda = 665$  nm) is not in line with the donor strength determined by the oxidation potential obtained from CV which might be due to the lower aromatic stabilization energy of the thiophene (compared to benzene). On the other hand, an inspection of full-width-at-half-maximum (FWHM) reveals a decrease of FWHM of the lowest absorption band in energy, which results in the same type of progression as that of absorption maxima such as **1** ( $3802\text{ cm}^{-1}$ ) > **2** ( $2805\text{ cm}^{-1}$ ) > **3** ( $2399\text{ cm}^{-1}$ ) > **4** ( $2303\text{ cm}^{-1}$ ) > **6** ( $1605\text{ cm}^{-1}$ ) > **5** ( $1457\text{ cm}^{-1}$ ). Note that the spectra of **1** – **2** possess the characteristic feature of a broad and structure-less charge transfer (CT) transition, which is not observed in the spectra of **3** – **6**. In other words, the spectra of **3** – **6** are not consistent with the notion that an increased donor strength correlates with a pronounced CT transition. Such results support the fact that first excited state of **1** – **2** and **3** – **6** do not have the same nature of electronic configuration.


Upon looking at PL spectra of **1**- **6** in DCM solution (Figure 2b), no spectral shift consistency is observed as donor strength increases. Red-shift occurs for **1** (714 nm) and **2** (736 nm) as expected. On the other hand, **3** (724 nm), **4** (698 nm) and **5** (703 nm) are blue-shifted compared to **2**. Such a discrepancy is also supported by the drastic change of FWHM going from the weakest donor (**1**) to the strongest one (**6**) as can be seen from Figure 2b. In more details, FWHM decreases from  $3267\text{ cm}^{-1}$  to  $2399\text{ cm}^{-1}$  when the donor strength is increased slightly from **1** to **2**. Then, FWHM gradually decreases down to  $1032\text{ cm}^{-1}$  and  $1013\text{ cm}^{-1}$  for **5** and **6**, respectively. In addition, it is important to notice that, while the emission for **1** and **2** is broad and structure-less as expected for CT emission, the emission for **3** – **6** is well-structured and not in line with CT-like emission. Those results also strongly suggest that, in solution, the electronic configuration nature of the lowest excited states for **1** – **2** is different from that of **5** – **6**. While for **1** – **2** CT excited states are involved in solution, for **5** – **6** polymethine-like character seems to be predominant in the lowest excited state.

**Table 2.** FWHM of absorption and photoluminescence spectra

Compound	<b>1</b>	<b>2</b>	<b>3</b>	<b>4</b>	<b>5</b>	<b>6</b>
Absorption FWHM ( $\text{cm}^{-1}$ )	3802	2805	2399	2303	1457	1605
Photoluminescence FWHM ( $\text{cm}^{-1}$ )	3267	2399	1567	1561	1032	1013

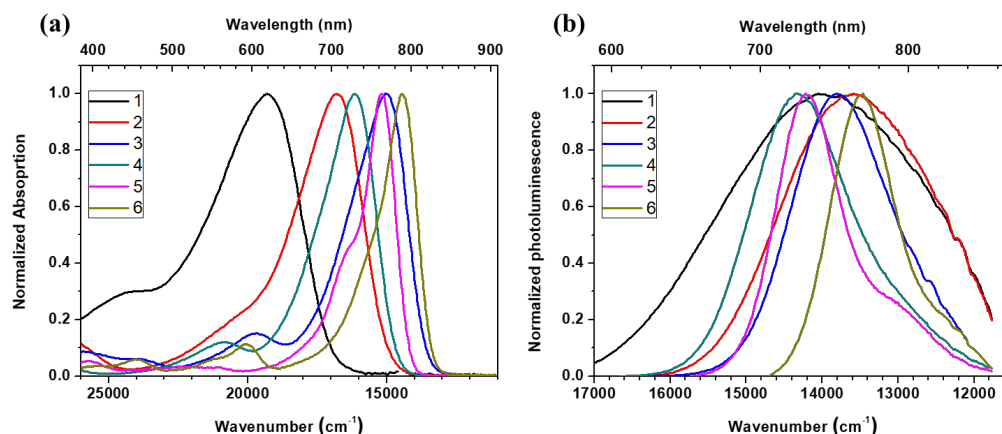

**Figure 2** (a) Normalized absorption spectra and (b) normalized photoluminescence spectra of compound **1** (exc.  $\lambda = 490\text{nm}$ ), compound **2** ( $560\text{nm}$ ), compound **3** ( $630\text{nm}$ ), compound **4** ( $580\text{nm}$ ), compound **5** ( $580\text{nm}$ ), and compound **6** ( $620\text{nm}$ ) Curc series dissolved in dichloromethane (DCM) at concentration  $< 10^{-6}$  mole per liter. See Table 2 for FWHM of absorption and photoluminescence spectra.

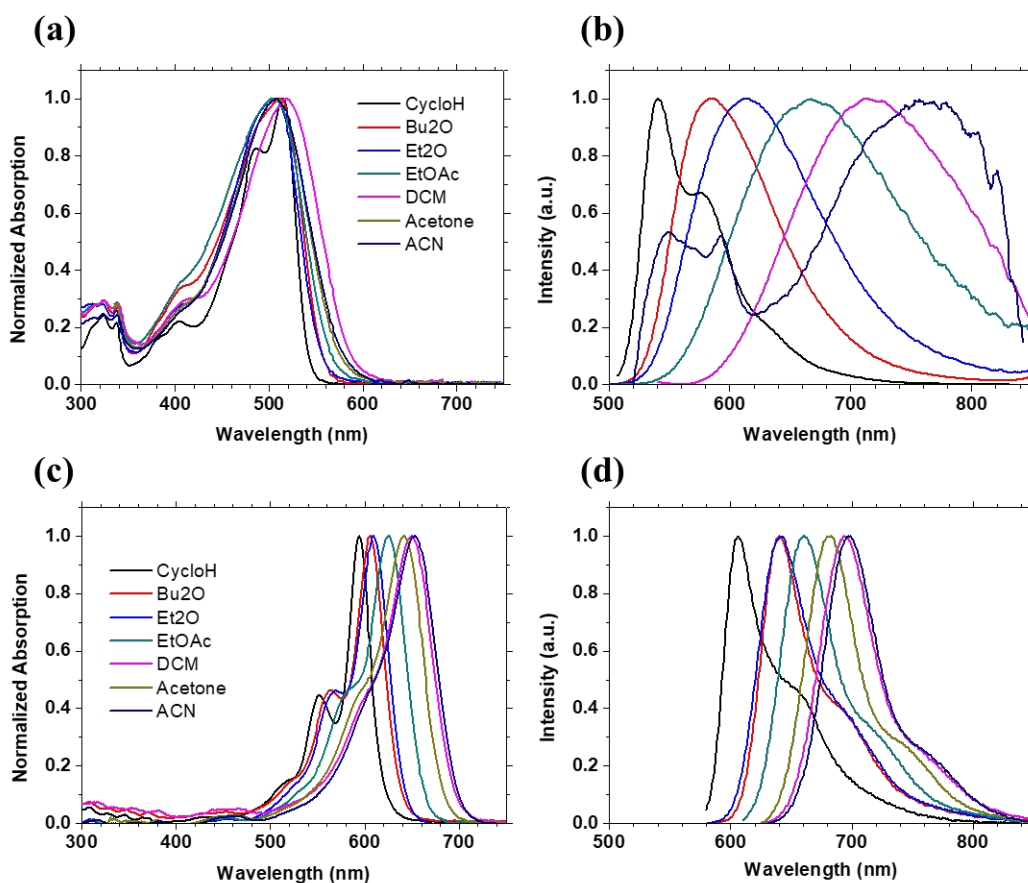

**Figure 3** Absorption spectra and photoluminescence spectra of compound **1** (a) and (b), compound **5** (c) and (d) in 7 solvents with different polarity (see Table S3 for the values of orientation polarizability).


To get a better insight into the nature of the lowest excited state, solvatochromism of six Curc series is measured in solvents with different polarity. Those data are analysed by using Lippert-Mataga formalism which gives the difference of dipole moment between the ground state and



excited state by considering the variation of Stokes shift ( $\Delta\nu$ ) as a function of the orientation polarizability of solvents ( $\Delta f^*$ ). [19, 20] Solvatochromisms of all six Curc series are shown as Lippert-Mataga plots in Figure 4. When increasing the polarity of the solvent, a large change of Stokes shift takes place for the weakest donor (slope of  $21364 \text{ cm}^{-1}$  for **1**, see Figure 4) while no substantial change of Stokes shift takes place for the strongest donor (slope of  $1675 \text{ cm}^{-1}$  for **6**, see Figure 4).

By comparing Lippert-Mataga plot (Figure 4) and PL spectra (Figure 2), the decrease of slope in Lippert-Mataga plot by almost 13-fold when the donor strength increased from **1** to **6** leads to the notion that the excited state nature of **6** is different from that of **1**. For **1**, the large Lippert-Mataga slope is accompanied by a broad and structure-less emission revealing a clear CT emission, while for **6** the small Lippert-Mataga slope is reinforced by the structuration of the emission band which is inconsistent with CT emission and more associated with polymethine-type emission. In fact, such behaviour is in line with charge delocalization and polymethine-type emission. Noticeably, a gradual decrease of the Lippert-Mataga slope upon increasing donor strength for **2**, **4** and **3** (see Figure 4) along with the structuration of emissions for **3** and **4** (See Figure 2b) indicates an increase of polymethine character compared to CT character. It is to be noted that a similar conclusion was drawn theoretically by Brédas *et al.* in literature on a dye of the same family as **2** [21] and on a dye containing a cyano unit in meso position of curcuminoid. [18] To support further this statement, Stokes shift of a polymethine model squaraine (See Figure S2 for molecular structure compound **7**) was examined. As displayed in Figure S3, structured UV/vis absorption and emission spectra are observed for this polymethine model squaraine, similar to those observed for compounds **5** and **6** in solvents with ten different polarities. Together with the small Lippert-Mataga slope of  $888 \text{ cm}^{-1}$  observed with the polymethine model squaraine in Figures 4 and 6, these results support well our claim that the increase of donor strength shifts the electronic configuration from CT excited state to polymethine-type excited state in the six Curc series.

Therefore, we conclude that while a clear CT emission is observed for **1**, this CT character of the emission gradually decreases upon increasing donor strength of the side groups, resulting in an increased polymethine character of Curc series. That is, CT character follows in sequence of **1** > **2** > **4** > **3** > **5** > **6**.

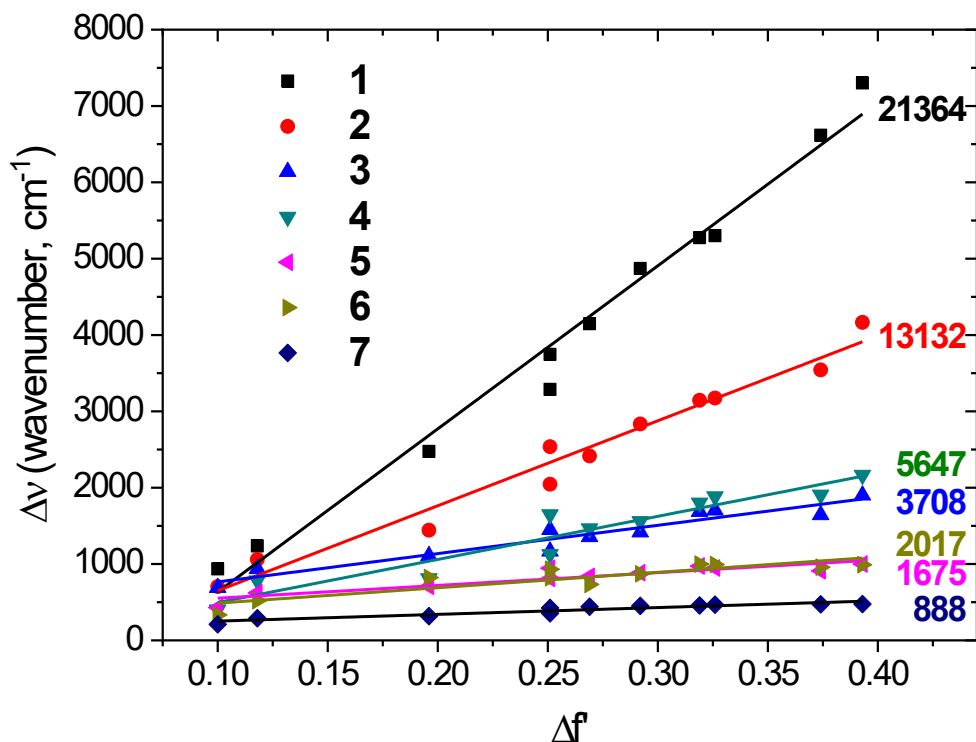

**Figure 4.** Lippert-Mataga plots of six Curc series molecules (1 – 6) are shown along with polymethine squaraine dye 7. Numbers on the right of straight lines are slope value. Orientation polarizabilities  $\Delta f$  of 11 solvents are listed in Table S3.

### 3. Donor strength dependence of optical property in thin film

The structural and optical properties of the series of six Curc in thin films were investigated to determine how the electron donor strength relates to their ENZ response. Each Curc dye was dissolved in chloroform at the concentration of 0.34 wt% (5mg/mL) and was spin-coated onto a fused silica substrate at the rate of 1000 rpm for 30s. The spin-coated Curc films showed thickness of 29.5 nm, 34.3 nm, 39.0 nm, 33.5 nm, 39.6 nm and 30.5 nm, respectively in the order of **1**, **2**, **3**, **4**, **5**, and **6**. Structural and ENZ properties of the six Curc series were characterized by measurements such as 2D grazing incidence X-ray scattering (GIWAXS), spectroscopic ellipsometry (SE), linear optical spectroscopy, and attenuated total reflection (ATR).

#### 3.1. Grazing incidence wide angle x-ray scattering (GIWAXS) measurement


Characterization of the structural and morphology properties of the spin-coated thin films of six Curc series was performed by 2D grazing incidence X-ray scattering experiments (Figure S4 and S5). Such experiments were done to determine whether the spin-coated films were structured or not. Therefore,

the obtained data were allowed to determine if the ellipsometry should be fitted as isotropic (no structuration) or uniaxial (for structured films). Films of **1** and **6** are found to be optically uniaxial, as they are partly structured in lamellar phases with lamellae parallel to substrate and without in-plane alignment. Films of **2**, **3**, **4**, and **5** are found to be isotropic. See SI for more description of the film investigation.

### 3.2. Spectroscopic ellipsometry measurement

The real and imaginary parts of the dielectric constants of the six Curc films were determined using spectroscopic ellipsometry (SE). This type of measurements was used to assess whether the real part of the permittivity is below 1 and thus conclude on the ENZ properties in a certain wavelength range. Magnitude  $\tan\Psi$  and phase  $e^{i\Delta}$  of the complex ratio of reflection coefficients  $R_s$  to  $R_p$  are measured and fitted to obtain the real part  $n$  and imaginary part  $k$  of refractive index. Based on the GIWAXS results, we adopted a uniaxial optical model to fit the data obtained in the anisotropic films of **1** and **6** while those of the films of **2**, **3**, **4**, and **5** were fitted by adopting an isotropic model. The real and imaginary parts of dielectric permittivity ( $\text{Re}\{\varepsilon\}$  and  $\text{Im}\{\varepsilon\}$ , respectively) were then obtained from the real part  $n$  and imaginary part  $k$  of refractive index. Refer to Experimental Section/Methods and SI for more details.

As shown in Figure 5, for films of **1** and **2**,  $\text{Re}\{\varepsilon\}$  is well above 1 with no ENZ spectral region. Differently, for isotropic films of **3**, **4**, **5** and anisotropic film **6**, there exists spectral regions where  $\text{Re}\{\varepsilon\}$  is less than 1, with corresponding ENZ features over the spectral range of 500~600 nm, 500~655 nm, 510~670 nm, and 550~625 nm, for **3**, **4**, **5**, and **6**, respectively. Table 3 also reports on the lowest value of  $\text{Re}\{\varepsilon\}$  with the corresponding spectral position in wavelength and ENZ spectral range (nm)  $-1 < \text{Re}\{\varepsilon\} < 1$  of six Curc series. We note that the width of the ENZ spectral region is broadened as donor strength increases for isotropic films of **3**, **4**, **5**. Notably, for isotropic films of **4** and **5** a double zero-crossing of  $\text{Re}\{\varepsilon\}$  takes place, similar to that observed in dielectric spectrum of squaraine indolenine triethyleneglycol molecular film.[22] That is, in films of **4** and **5**, as wavelength increases from blue to red spectral region,  $\text{Re}\{\varepsilon\}$  changes sign from positive to negative (ENZ) at short wavelength, while from negative to positive (Epsilon-Near-Pole, ENP) at long wavelength.[27-28] The presence of ENP is associated with a high value of refractive index  $n$ , and in fact the maximum value of  $n$  is over 3 in films of **4** and **5**. See Fig.S7 (d) and (e). When ENZ properties of anisotropic film **6** (the highest donor strength) and isotropic film **5** (the next highest donor strength) films are compared, we find that anisotropic structural formation significantly diminishes the imaginary part  $k$  of refractive index in film of **6**, resulting in no zero-crossing of  $\text{Re}\{\varepsilon\}$  in both parallel and perpendicular components. See Fig.S7 for dispersion of  $n$  and  $k$ .

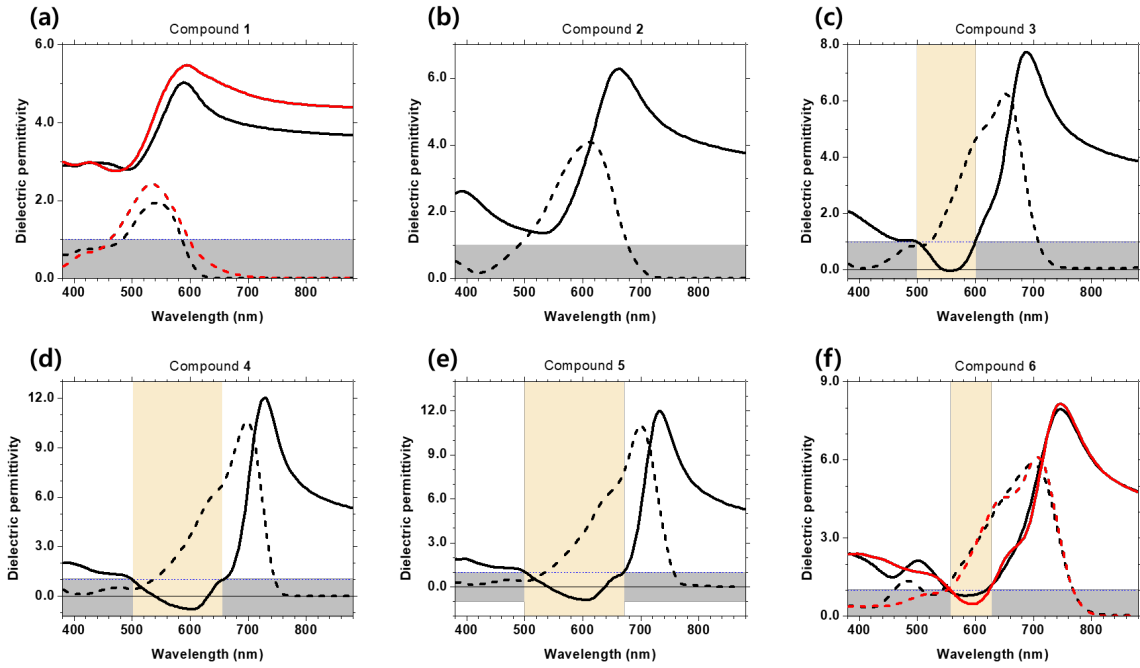


**Figure 5** Dielectric permittivity spectra of the six Curc series are plotted in increasing order of donor strength from (a) to (f). Solid (dashed) black and red curves refer to the real (imaginary) part of dielectric permittivity. In (a) and (f) black and red curves correspond to parallel and perpendicular components of dielectric permittivity, respectively.

**Table 3.** The lowest values of  $\text{Re}\{\epsilon\}$  with the corresponding spectral position in wavelength and ENZ spectral range (nm)  $-1 < \text{Re}\{\epsilon\} < 1$  of six Curc series

	Lowest value of $\text{Re}\{\epsilon\}$	Wavelength (nm)	ENZ spectral range (nm) $-1 < \text{Re}\{\epsilon\} < 1$
<b>Compound 1</b>	2.8	495	N/A
<b>Compound 2</b>	1.2	531	N/A
<b>Compound 3</b>	-0.1	560	500~600
<b>Compound 4</b>	-0.9	600	500~655
<b>Compound 5</b>	-1.0	605	500~670
<b>Compound 6</b>	0.2	600	550~625


### 3.3 Linear optical spectroscopy of reflection, transmission, and absorption

Linear optical spectra of six Curc series thin films are shown in Figure 6, including (a) reflection, (b), transmission, and (c) normalized absorbance ( $-\log(R+T)$ ). Several features in those linear spectra are noted. First, it is found that the reflections of 3, 4, 5 and 6 are more intense than those of 1 and 2, indicating that the reflection becomes stronger as the donor strength increases. Second, a larger red-shift of the absorption peak takes place as the donor strength increases. This is due to the auxochrome function of the end groups on the phenyl or thiophene as well as the longer polymethine. Together with the ellipsometric data, those results clarify the impact of the donor strength and the polymethine character on the optical properties of the films.

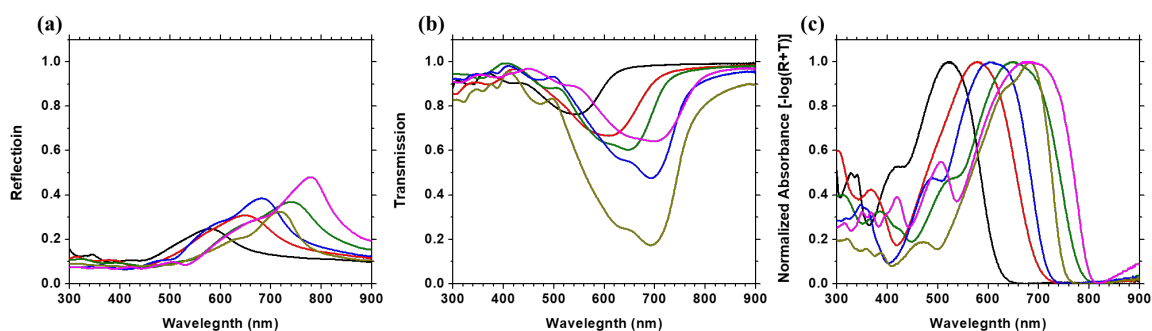

**Figure 6.** Linear optical spectra of the six Curc series in thin films. (a) Reflection, (b) Transmission, and (c) Normalized Absorbance. Compound 1 as black curve, compound 2 as red curve, compound 3 as blue curve, compound 4 as green curve, compound 5 as gold curve, and compound 6 as pink curve number.


### 3.4 FDTD simulation of linear optical spectra of film 5 and Attenuated total reflection measurement

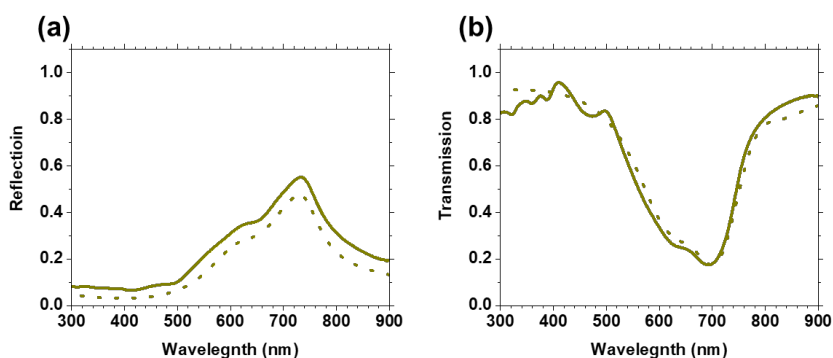

**Figure 7.** Experimental (solid curve) and FDTD simulated (dashed curve) reflection (a) and transmission (b) spectra of film 5 are compared.

Measured reflection and transmission spectra of film **5** are shown in Figure 7. Reflection in the visible spectral range is observed with maximum peak location of 735 nm for a value of 55%. In parallel, the transmission exhibits the lowest value of 17.4% at a wavelength of 694 nm. Those spectra were also simulated using finite-difference time domain (FDTD) and the calculated spectra well correlated with the experimental data confirm the adequacy of the permittivity values extracted from SE measurements.

Attenuated total internal reflection (ATR) measurements were carried out to identify surface exciton polariton excitation in the Curc films.[11] The films spin-coated on top of fused silica substrate were combined with a coupling prism in the Kretschmann geometry where the reflectivity is measured as a function of the angle of incidence. In this measurement, a sharp minimum in the reflectivity can be observed under the resonant conditions when the light is coupled to the surface exciton polaritons.

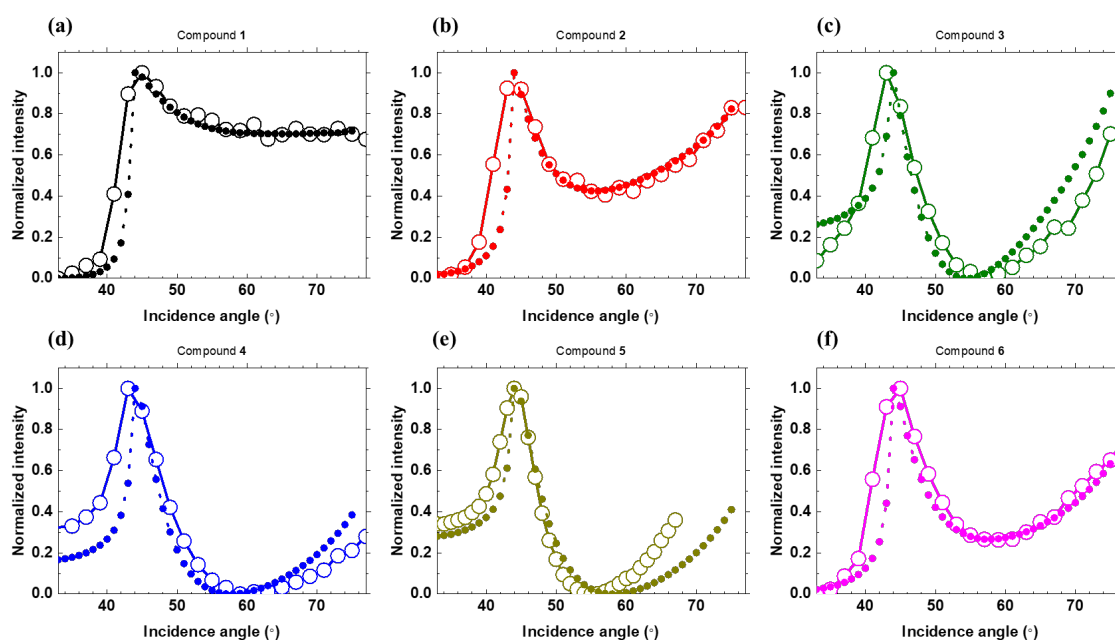

**Figure 8.** Experimental (open circle) and FDTD simulated (closed circle) ATR spectra for six Curc series.

ATR spectra of six Curc series shown in Fig. 8 were measured at the wavelength of the minimum  $\text{Re}\{\varepsilon\}$  (see Table 3) and show that the ATR resonance takes place in the spectral region of  $\text{Re}\{\varepsilon\} < -1$ . In particular, among ATR spectra of the isotropic films of **2**, **3**, **4**, and **5** in Figure 8 (b), (c), (d), and (e), it can be seen that ATR resonance is more pronounced in sequence of (c), (d), and (e) following the lowest  $\text{Re}\{\varepsilon\}$  value, *i.e.*, -0.1, -0.9, and -1.0, for compound **3**, **4**, and **5**, respectively. Notably, Figure 8 (d) and (e) show a well-defined ATR resonance as a function of incidence angle. In ATR spectra of the anisotropic films of **1** and **6** in Figure 8 (a) and (f), both spectra do not show ATR resonance, where the lowest  $\text{Re}\{\varepsilon\}$  values are above 0, *i.e.*, 2.8 and 0.2 for compound **1** and **6**, respectively. Importantly, it

can be seen that the experimental ATR data are in good consistency with FDTD calculations, providing further evidence of the ENZ response supporting surface exciton polaritons in some of the Curc films.

#### **4. Discussion**

By varying the donor strength at the end groups of Curc series, the structure-property relationship between donor strength and polymethine character is clearly identified. As the donor strength increases, the polymethine character in solution becomes dominant while the CT character diminishes. Within the examples reported here, we showed that the polymethine character can be correlated to some extent to the presence and the broadening of ENZ spectral region in pristine thin film. The dyes with CT character work efficiently for emissive organic electronics applications[21, 23, 24] while not showing ENZ properties. On the other hand, the polymethine character in Curc dyes is associated with characteristics related to ENZ materials. In other words, the identification of excited-state electronic nature in solution guides which dye might possess ENZ properties in their pristine form: (i) the dye with CT character can be excluded as candidates for ENZ thin film and (ii) the dyes having polymethine character can be tested to see whether the ENZ properties exist in thin film, which seems to be effective all the time in the present case. The reason why those Curc with polymethine character shows ENZ properties is still under investigation: this might be related to (i) the intense and narrow absorption of the polymethine (however, this is not observed experimentally in the thin films) or (ii) to the presence of intermolecular CT states formed when strong electron-donor side groups stacks on strong electron-withdrawing groups (i.e. central AcacBF<sub>2</sub>)[25]. In the latter case, photoinduced hole and electrons are formed.

Based on the analysis of film structure obtained from GIWAXS and SE measurements, it is found that the tiny structuration induces an optically uniaxial films which possess ENZ spectral region narrower than optically isotropic films. In other words, even though polymethine character in solution is more dominant in compound **6** than compound **5**, ENZ property is more prominent in isotropic film of compound **5** than uniaxial film of compound **6**.

Therefore, two factors of the strong donor strength (dominant polymethine character in solution) in Curc dye and the isotropy in film structure are key in obtaining a prominent ENZ property with a broader spectral range. Finally, in the case of Curc ENZ film, the surface exciton polariton excitation within the ENZ spectral range was confirmed by use of ATR technique and FDTD simulations, ensuring that the observed ENZ region (resulting from the SE fits) presents a pronounced ATR resonance. This study opens a novel path toward the development of new organic materials with ENZ properties in the visible and near infrared spectral range.

#### **5. Conclusion**

In conclusion, through increasing the donor strength in a Curc series with a D-A-D structure, the CT character diminishes and the polymethine character became more pronounced and dominant. The compounds with the strong polymethine character in solution were found to exhibit an ENZ spectral region in pristine molecular film. Furthermore, the manner of how the molecules are arranged on the film is shown to determine optical anisotropy as well as the feature of ENZ response. Out of the six Curc thin films four showed an ENZ response, all in the visible spectrum range, ranging from 500 nm to 670 nm. Overall with increasing polymethine character in solution, we were able to design, synthesize and characterize Curc dyes forming ENZ response exhibiting ENP as well as ENZ. These results provide new important guidelines that should be taken into account when designing molecular systems with ENZ properties in thin films.



## 6. Experimental Section/Methods

### 1. [Materials and Methods]

All solvents for synthesis were of analytic grade. NMR spectra ( $^1\text{H}$  and  $^{13}\text{C}$ ) were recorded at room temperature on JEOL JNM ECS 400 operating at 400 and 100 MHz for  $^1\text{H}$  and  $^{13}\text{C}$ , respectively. Data are listed in parts per million (ppm) and are reported relative to tetramethylsilane ( $^1\text{H}$  and  $^{13}\text{C}$ ); residual solvent peaks of the deuterated solvents were used as internal standards. Mass spectra were realized in Spectropole de Marseille (<http://www.spectropole.fr/>). Compound **2** has been reported elsewhere.[26] The UV/vis absorption spectra were measured using Hitachi spectrophotometer U-3900 with a double beam single monochromator system. Reflection and transmission were measured independently for films. The absorbance was calculated by using  $\text{Absorbance} = -\log(R+T)$ . The fluorescence spectra were measured using a Horiba Jobin Yvon fluorimeter (FluoroMax-4).

### 2. [Grazing-Incidence Wide-Angle X-ray Scattering]

The characterization of the structural and morphology properties of the spin-coated Curc thin films was performed by 2D grazing incidence X-ray scattering experiments at PLS-II 9A 9A U-SAXS beamline of Pohang Accelerator Laboratory in Korea. The thin films were studied on silicon substrates and the X-rays coming from the in-vacuum Undulator (IVU) were monochromated using Si(111) double crystals and focused on a detector consisting of a 2D CCD detector (Rayonix SX165). The distance between sample and detector was around 221 mm for a beam energy of 11.055 keV (1.100 Å).

### 3. [Spectroscopic Ellipsometry]

A J. A. Woollam co. alpha-SE spectroscopy ellipsometer was used to measure  $\Psi$  and  $\Delta$  between 381 and 887 nm at an angle of incidence of  $70^\circ$ , both parameters describing the output elliptical polarization state after linearly polarized light is reflected off of the thin film. Note that the light beam illuminating the samples had a diameter of  $\sim 2\text{mm}$ . After measuring  $\psi$  and  $\Delta$ , a model was built using the analysis software CompleteEASE® program in order to determine the optical constants and the dielectric permittivity of the films. Average mean-square-error (MSE) is from 2 to 3. See supporting Information for detailed analysis of modeling and fitting of each film.

### 4. [Attenuated Total Reflection]

Home-built setup of a Kretschmann geometry is used with a fiber-coupled Deuterium-Halogen lamp (Ocean Optics, DH2000) light source with a polarizer allowing the light to be p-polarized at a wavelength range of 400-800 nm. The beam is focused using a convex lens and a BK-7 glass prism

mounted on a rotating holder with a varying incidence angle from 30° to 80°. The thin films, prepared on fused silica, are coupled to the prism with index-matching oil ( $n=1.51$ ). The reflected light is detected using a fiber-coupled spectrometer (Ocean Optics, HR4000CG-UVNIR).

## 5. [Finite Difference Time Domain]

Finite-difference time-domain (FDTD, Lumerical) simulations were used to calculate the reflection, transmission, and ATR and were then compared to the experiment data. The film thickness of the organic thin films obtained through surface profilometry (Dektak) measurements were used along with the permittivity values obtained through spectroscopy ellipsometry for simulation.

## 6. [Synthesis of **1** and **4**]

In a 100 mL flask, acetylacetone (5.0 mmol, 1 eq) and  $\text{BF}_3\cdot\text{Et}_2\text{O}$  (600  $\mu\text{L}$ , 5.25 mmol, 1.05 eq) in 3mL of ethyl acetate were heated for 30min at 50-60 °C in air. Dissolved aldehyde (10.1 mmol, 2.1 eq) and  $\text{B}(\text{n-OBu})_3$  (10.1 mmol, 2.1 eq) into 40mL ethyl acetate, then the solution was injected into the first mixture. The reaction was kept at 50-60°C for another 30 min. First portion of butylamine (2.0 mmol, 0.4 eq) was added dropwise into the reaction and the reaction was kept heating at 50-60°C overnight. All the solvents were evaporated. The crude product could be obtained by flash column chromatography (silica,  $\text{CH}_2\text{Cl}_2$ ). Further purification was done by many times' precipitation in  $\text{CH}_2\text{Cl}_2$ /petroleum ether, giving dark green powder.

9,9'-(((1E,1'E)-(2,2-difluoro-5-phenyl-2H-113,3,214-dioxaborinine-4,6-diyl)bis(ethene-2,1-diyl))bis(4,1-phenylene))bis(9H-carbazole) **1** (992 mg, 77% yield).  $^1\text{H}$  NMR (400 MHz,  $\text{CDCl}_3$ , ppm): 8.21(d,  $^3J= 15.6$  Hz, 2H), 8.14 (d,  $^3J= 8.0$  Hz, 4H), 7.72 (d,  $^3J= 8.8$  Hz, 4H), 7.64 (d,  $^3J= 8.8$  Hz, 4H), 7.59 (m, 3H), 7.45 (m, 10H), 7.31 (dt,  $^3J= 8.0$  Hz,  $^4J= 1.5$  Hz, 4H), 6.70 (d,  $^3J= 15.6$  Hz, 2H);  $^{13}\text{C}$  NMR (100 MHz,  $\text{CDCl}_3$ , ppm): Not soluble enough. HRMS (ESI+)  $[\text{M} + \text{Na}]^+$  calcd for  $\text{C}_{49}\text{H}_{33}\text{N}_2\text{O}_2\text{BF}_2\text{Na}^+$   $m/z= 753.2504$ , found  $m/z= 753.2502$ .

4,4'-(((1E,1'E)-(2,2-difluoro-2H-113,3,214-dioxaborinine-4,6-diyl)bis(ethene-2,1-diyl))bis(N,N-dibutylaniline) **4** (712 mg, 22% yield).  $^1\text{H}$  NMR (400 MHz,  $\text{CD}_2\text{Cl}_2$ , ppm): 7.87 (d,  $^3J= 15.2$  Hz, 2H), 7.50 (d,  $^3J= 9.2$  Hz, 4H), 6.66 (d,  $^3J= 9.2$  Hz, 4H), 6.46 (d,  $^3J= 15.2$  Hz, 2H), 5.90 (s, 1H), 3.36 (t,  $^3J= 8.0$  Hz, 8H), 1.61 (m, 8H), 1.38 (m, 8H), 0.97 (t,  $^3J= 7.6$  Hz, 12H);  $^{13}\text{C}$  NMR (100 MHz,  $\text{CD}_2\text{Cl}_2$ , ppm): 177.25, 151.18, 146.21, 131.70, 121.47, 114.08, 111.66, 100.70, 50.87, 29.40, 20.28, 13.75. HRMS (ESI+)  $[\text{M} + \text{Na}]^+$  calcd for  $\text{C}_{49}\text{H}_{33}\text{N}_2\text{O}_2\text{BF}_2\text{Na}^+$   $m/z= 601.3753$ , found  $m/z= 601.3757$ .

## 7. [Synthesis of **3**, **5** and **6**]

The synthesis of **3**, **5** and **6** were done similarly to the ones of **1** and **4** by substituting n-butylamine by morpholine.

5,5'-((1E,1'E)-(2,2-difluoro-2H-113,3,214-dioxaborinine-4,6-diyl)bis(ethene-2,1-diyl))bis(N,N-diphenylthiophen-2-amine) **3** (521 mg, 43% yield)

<sup>1</sup>H NMR (400 MHz, CD<sub>2</sub>Cl<sub>2</sub>, ppm): 7.91 (d, <sup>3</sup>J = 15.9 Hz, 2H), 7.38 (m, 8H), 7.22 (m, 14H), 6.39 (d, <sup>3</sup>J = 4.0 Hz, 2H), 5.98 (d, <sup>3</sup>J = 15.9 Hz, 2H), 5.63 (s, 1H); <sup>13</sup>C NMR (100 MHz, CDCl<sub>3</sub>, ppm): 176.49, 161.47, 146.67, 139.02, 137.37, 130.31, 129.11, 126.56, 125.85, 114.88, 114.81, 101.57. HRMS (ESI+) [M + Na]<sup>+</sup> calcd for C<sub>39</sub>H<sub>29</sub>N<sub>2</sub>O<sub>2</sub>S<sub>2</sub>BF<sub>2</sub>Na<sup>+</sup> m/z = 693.1629, found m/z = 693.1635.

(2E,2'E)-2,2'-((2E,2'E)-(2,2-difluoro-2H-113,3,214-dioxaborinine-4,6-diyl)bis(prop-2-en-3-yl-1-ylidene))bis(1,3,3-trimethylindoline) **5** (448 mg, 32% yield)

<sup>1</sup>H NMR (400 MHz, DMSO-*d*<sub>6</sub>, ppm): 8.30 (t, <sup>3</sup>J = 13.6 Hz, <sup>3</sup>J = 13.2 Hz, 2H), 7.95 (d, <sup>3</sup>J = 7.2 Hz, 4H), 7.15 (t, <sup>3</sup>J = 7.0 Hz, 4H), 6.69 (s, 1H), 6.12 (d, <sup>3</sup>J = 14.0 Hz, 2H), 5.94 (d, <sup>3</sup>J = 13.2 Hz, 2H), 3.50 (s, 6H) 1.57 (s, 12H); <sup>13</sup>C NMR (100 MHz, DMSO-*d*<sub>6</sub>, ppm): Not soluble enough. HRMS (ESI+) [M + Na]<sup>+</sup> calcd for C<sub>31</sub>H<sub>33</sub>N<sub>2</sub>O<sub>2</sub>BF<sub>2</sub>Na<sup>+</sup> m/z = 537.2501, found m/z = 537.2507.

5,5'-((1E,1'E)-(2,2-difluoro-2H-113,3,214-dioxaborinine-4,6-diyl)bis(ethene-2,1-diyl))bis(N,N-dibutylthiophen-2-amine) **6** (616 mg, 29% yield) <sup>1</sup>H NMR (400 MHz, CDCl<sub>3</sub>, ppm): 7.90 (d, <sup>3</sup>J = 14.8 Hz, 2H), 7.10 (d, <sup>3</sup>J = 4.0 Hz, 2H), 5.85 (d, <sup>3</sup>J = 4.4 Hz, 2H), 5.81 (d, <sup>3</sup>J = 14.4 Hz, 2H), 5.99 (s, 1H), 3.33 (t, <sup>3</sup>J = 7.6 Hz, 8H), 1.65 (m, 8H), 1.36 (m, 8H), 0.97 (d, <sup>3</sup>J = 7.2 Hz, 12H); <sup>13</sup>C NMR (100 MHz, CDCl<sub>3</sub>, ppm): 174.49, 164.04, 138.67, 138.09, 123.36, 110.75, 103.92, 99.67, 53.61, 29.16, 20.17, 13.83. HRMS (ESI+) [M + Na]<sup>+</sup> calcd for C<sub>39</sub>H<sub>57</sub>N<sub>2</sub>O<sub>2</sub>BF<sub>2</sub>Na<sup>+</sup> m/z = 613.2881, found m/z = 613.2878.

## 8. [Film Fabrication]

The organic ENZ thin films of curcuminoid were prepared on fused silica and silicon substrates. The fused silica substrates were cut in advance into square pieces with the size of 2.0 cm x 2.0 cm in order to fully cover the prism area of the ATR experiment. The substrates were washed using acetone, isopropyl alcohol (IPA), and chloroform each for 10 minutes in an ultrasonic bath, afterwards the excess liquid was dried off with N<sub>2</sub> gas. The synthesized organic potential ENZ molecules of 5mg are dissolved in 1 mL of chloroform. The ENZ thin films were prepared by spin-coating the solution onto fused silica or silicon substrates at 1000 rpm for 30s. As a result, approximate film thicknesses were between 30 and 40 nm for each film determined by Dektak and also Spectroscopic Ellipsometry. No further processing such as thermal annealing of the thin film was made in this study.

## Supporting Information

Supporting Information is available from the Wiley Online Library.

### Author contribution

Kyu-Ri Choi, Dae Hyeon Kim and Steven Huynh prepared the films, optimized film thickness, and carried out spectroscopic ellipsometry measurement. Kyu Ri Choi and Yeon Ui Lee set up ATR measurement and performed FDTD. Virginie Placide, Fabrice Mathevet, and Benoît Heinrich performed GIWAXS measurement. Dandan Yao, Elena Zaborova, Frédéric Fages, and Anthony D'Aléo synthesized molecules. Gabriel Canard performed electrochemistry characterization. Loïc Mager helped on the optics of ATR measurement. Jean-Charles Ribierre helped on physics of ENZ film. Jeong Weon Wu, Jean-Charles Ribierre, Frédéric Fages, and Anthony D'Aléo wrote the manuscript. Anthony D'Aléo and Frédéric Fages worked on photophysics of the dyes. Jeong Weon Wu, Frédéric Fages, and Anthony D'Aléo designed project.

### Conflicts of interest

There are no conflicts of interest to declare.

### Acknowledgements

This work is supported by funding of the Ministry of Science, ICT & Future Planning, Korea (2014M3A6B3063708, 2017R1E1A1A01075394). YUL acknowledges National Research Foundation for funding (2021R1F1A1062916). This work was carried out in the framework of CNRSUMI2002 2B-FUEL "Building Blocks for Future Electronics Laboratory". We further thank Pohang Accelerator Laboratory (PAL) for giving us the opportunity to perform the GIWAXS measurements, MEST and POSTECH for supporting these experiments, Dr Hyungju Ahn for adjustments and help, and other colleagues from the 9A USAXS beamline for assistance. Part of this work was also supported by the CNRS (PICS No 8085), France.

### References

1. Liberal, I. and N. Engheta, *Near-zero refractive index photonics*. Nature Photonics, 2017. **11**(3): p. 149-158.
2. Alam, M.Z., I. De Leon, and R.W. Boyd, *Large optical nonlinearity of indium tin oxide in its epsilon-near-zero region*. Science, 2016. **352**(6287): p. 795-797.
3. Kinsey, N. and J. Khurgin, *Nonlinear epsilon-near-zero materials explained: opinion*. Optical Materials Express, 2019. **9**(7): p. 2793-2796.
4. Alam, M.Z., et al., *Large optical nonlinearity of nanoantennas coupled to an epsilon-near-zero*

- material. *Nature Photonics*, 2018. **12**(2): p. 79-83.
5. Alù, A., et al., *Epsilon-near-zero metamaterials and electromagnetic sources: Tailoring the radiation phase pattern*. *Physical Review B*, 2007. **75**(15): p. 155410.
  6. Enoch, S., et al., *A Metamaterial for Directive Emission*. *Physical Review Letters*, 2002. **89**(21): p. 213902.
  7. Maas, R., et al., *Experimental realization of an epsilon-near-zero metamaterial at visible wavelengths*. *Nature Photonics*, 2013. **7**(11): p. 907-912.
  8. Atkinson, R., et al., *Anisotropic optical properties of arrays of gold nanorods embedded in alumina*. *Physical Review B*, 2006. **73**(23): p. 235402.
  9. Caspani, L., et al., *Enhanced Nonlinear Refractive Index in Epsilon-Near-Zero Materials*. *Physical Review Letters*, 2016. **116**(23): p. 233901.
  10. Kinsey, N., et al., *Epsilon-near-zero Al-doped ZnO for ultrafast switching at telecom wavelengths*. *Optica*, 2015. **2**(7): p. 616-622.
  11. Lee, Y.U., et al., *Organic Monolithic Natural Hyperbolic Material*. *ACS Photonics*, 2019. **6**(7): p. 1681-1689.
  12. Lee, Y.U., et al., *Strong Nonlinear Optical Response in the Visible Spectral Range with Epsilon-Near-Zero Organic Thin Films*. *Advanced Optical Materials*, 2018. **6**(14): p. 1701400.
  13. Gentile, M.J., S. Núñez-Sánchez, and W.L. Barnes, *Optical Field-Enhancement and Subwavelength Field-Confinement Using Excitonic Nanostructures*. *Nano Letters*, 2014. **14**(5): p. 2339-2344.
  14. Cacciola, A., et al., *Subdiffraction Light Concentration by J-Aggregate Nanostructures*. *ACS Photonics*, 2015. **2**(7): p. 971-979.
  15. Woo, B.H., et al., *Dispersion Control of Excitonic Thin Films for Tailored Superabsorption in the Visible Region*. *ACS Photonics*, 2017. **4**(5): p. 1138-1145.
  16. Gu, L., et al., *Quest for organic plasmonics*. *Applied Physics Letters*, 2013. **103**(2): p. 021104.
  17. Zhu, G., et al., *Gigantic Optical Nonlinearity: Laser-Induced Change of Dielectric Permittivity of the Order of Unity*. *ACS Photonics*, 2015. **2**(5): p. 622-627.
  18. Polishchuk, V., et al., *D- $\pi$ -A- $\pi$ -D Dyes with a 1,3,2-Dioxaborine Cycle in the Polymethine Chain: Efficient Long-Wavelength Fluorophores*. *European Journal of Organic Chemistry*, 2018. **2018**(2): p. 240-246.
  19. Lippert, E., *Dipolmoment und Elektronenstruktur von angeregten Molekülen*. *Zeitschrift für Naturforschung A*, 1955. **10**(7): p. 541-545.
  20. Noboru, M., K. Yozo, and K. Masao, *Solvent Effects upon Fluorescence Spectra and the Dipolemoments of Excited Molecules*. *Bulletin of the Chemical Society of Japan*, 1956. **29**(4): p. 465-470.
  21. Kim, D.-H., et al., *High-efficiency electroluminescence and amplified spontaneous emission from a thermally activated delayed fluorescent near-infrared emitter*. *Nature Photonics*, 2018. **12**(2): p. 98-104.
  22. Minjae Kim, K.R.C., Yeon Ui Lee, Benoît Heinrich, Soo Young Ko, Fabrice Mathevet, Jean-Charles Ribierre, Anthony D'Aléo, Jeong Weon Wu, Virginie Placide, *Natural hyperbolic dispersion with anisotropic epsilon-near-zero and epsilon-near-pole in squaraine molecular film*. *Advanced Optical Materials*, 2021.
  23. Ye, H., et al., *Near-Infrared Electroluminescence and Low Threshold Amplified Spontaneous Emission above 800 nm from a Thermally Activated Delayed Fluorescent Emitter*. *Chemistry of Materials*, 2018. **30**(19): p. 6702-6710.
  24. Aoki, R., et al., *Realizing Near-Infrared Laser Dyes through a Shift in Excited-State Absorption*. *Advanced Optical Materials*, 2021. **9**(6): p. 2001947.
  25. Gillett, A.J., et al. *Spontaneous exciton dissociation enables spin state interconversion in delayed fluorescence organic semiconductors*. 2021. arXiv:2106.15512.
  26. Archet, F., et al., *Synthesis of Bioinspired Curcuminoid Small Molecules for Solution-Processed Organic Solar Cells with High Open-Circuit Voltage*. *ACS Energy Letters*, 2017. **2**(6): p. 1303-1307.
  27. Shekhar, Prashant, Jonathan Atkinson, and Zubin Jacob, *Hyperbolic metamaterials: fundamentals and applications* *Nano convergence*, 2014. **1** (1): p. 1-17.
  28. Starko-Bowes, Ryan, et al., *Optical characterization of epsilon-near-zero, epsilon-near-pole, and hyperbolic response in nanowire metamaterials*. *JOSA B*, 2015 **32**(10): p. 2074-2080.

## Supporting Information

### Effect of the electron donating group on excited-state electronic nature and epsilon-near-zero properties of curcuminoid-borondifluoride dyes

*Kyu-Ri Choi<sup>1</sup>, Dae Hyeon Kim<sup>1</sup>, Yeon Ui Lee<sup>2</sup>, Virginie Placide<sup>1</sup>, Steven Huynh<sup>1</sup>, Dandan Yao<sup>3</sup>, Gabriel Canard<sup>3</sup>, Elena Zaborova<sup>3</sup>, Fabrice Mathevet<sup>4,7</sup>, Loïc Mager<sup>5</sup>, Benoît Heinrich<sup>5</sup>, Jean-Charles Ribierre<sup>6</sup>, Jeong Weon Wu,<sup>1\*</sup> Frédéric Fages,<sup>3\*</sup> Anthony D'Aléo<sup>3,5\*</sup>*

<sup>1</sup> *Department of Physics, Ewha Womans University, Seoul 03760, Republic of Korea*

<sup>2</sup> *Department of Physics, Chungbuk National University, Chungbuk 28644, Republic of Korea*

<sup>3</sup> *Aix Marseille Univ, CNRS, CINaM UMR 7325, Campus de Luminy, Case 913, 13288 Marseille, France*

<sup>4</sup> *Sorbonne Universités, Faculté des Sciences, CNRS, Parisien de Chimie Moléculaire (IPCM), UMR 8232, Chimie des Polymères, 75005 Paris, France*

<sup>5</sup> *Université de Strasbourg, CNRS, Institut de Physique et Chimie des Matériaux de Strasbourg, UMR 7504, F-67000 Strasbourg, France*

<sup>6</sup> *Center for Organic Photonics and Electronics Research (OPERA), Kyushu University, Fukuoka 819-0395, Japan*

## **Contents**

1. Table of spectroscopic data and photophysical properties
2. Cyclic voltammetry data
3. Squaraine solvatochromism
4. Grazing incidence wide angle x-ray scattering (GIWAXS)
5. Spectroscopic ellipsometry measurement
6. Reflection, transmission, absorption measurements and FDTD data

## 1. Table of spectroscopic data and photophysical properties

Absorption spectra was measured on Hitachi spectrophotometer U-3900, a double beam single monochromator system. Fluorescence spectra was measured on Horiba Jobin Yvon fluorimeter FluoroMax-4.

**Table S1.** Spectroscopic data and photophysical properties of compounds **1**, **2** and **3** in solvents of different polarity at room temperature<sup>a</sup>

solvent	<b>1</b>			<b>2</b>			<b>3</b>		
	$\lambda_{\text{abs}}$	$\lambda_{\text{em}}$	$\Delta\nu_{ST}$	$\lambda_{\text{abs}}$	$\lambda_{\text{em}}$	$\Delta\nu_{ST}$	$\lambda_{\text{abs}}$	$\lambda_{\text{em}}$	$\Delta\nu_{ST}$
Cyclo	514	540	937	560	583	704	612	639	690
CCl <sub>4</sub>	522	558	1236	565	601	1060	626	665	937
Bu <sub>2</sub> O	511	585	2475	564	614	1444	622	668	1107
Et <sub>2</sub> O	506	607	3288	562	635	2046	624	673	1167
Chloroform	524	652	3747	593	698	2537	661	731	1449
BuOAc	507	642	4148	567	657	2416	631	690	1355
EtOAc	504	668	4871	568	677	2834	636	699	1417
DCM	516	709	5275	595	735	3201	665	749	1686
DCE	519	716	5301	594	732	3174	665	750	1704
Acetone	507	763	6618	580	730	3543	651	729	1644
ACN	507	805	7302	583	770	4166	661	756	1901

<sup>a</sup> Absorption maximum wavelengths  $\lambda_{\text{abs}}$  (nm). Fluorescence maximum wavelengths  $\lambda_{\text{em}}$  (nm). Stokes shifts  $\Delta\nu_{ST}$  (cm<sup>-1</sup>). Cyclo: Cyclohexane. CCl<sub>4</sub>: Carbon tetrachloride. Bu<sub>2</sub>O: n-Dibutylether. Et<sub>2</sub>O: Diethyl ether. BuOAc : n-Butylacetate. EtOAc: Ethyl acetate. DCM: Dichloromethane. DCE: 1,2-Dichloroethane. ACN: Acetonitrile.



**Table S2.** Spectroscopic data and photophysical properties of compounds **4**, **5** and **6** in solvents of different polarity at room temperature<sup>a</sup>

solvent	<b>4</b>			<b>5</b>			<b>6</b>		
	$\lambda_{\text{abs}}$	$\lambda_{\text{em}}$	$\Delta\nu_{ST}$	$\lambda_{\text{abs}}$	$\lambda_{\text{em}}$	$\Delta\nu_{ST}$	$\lambda_{\text{abs}}$	$\lambda_{\text{em}}$	$\Delta\nu_{ST}$
Cyclo	562	575	402	594	606	333	620	637	430
CCl <sub>4</sub>	574	601	783	610	630	520	633	659	623
Bu <sub>2</sub> O	574	602	810	608	640	901	636	666	708
Et <sub>2</sub> O	576	616	1127	609	641	820	640	675	810
Chloroform	609	677	1649	643	684	932	682	729	945
BuOAc	586	641	1464	625	655	733	655	693	837
EtOAc	591	651	1559	625	661	871	660	701	886
DCM	620	698	1802	649	694	999	692	742	974
DCE	620	702	1884	651	696	993	695	744	948
Acetone	609	689	1907	641	683	959	681	726	910
ACN	618	713.5	2166	652	697	990	696	748	998


<sup>a</sup> Absorption maximum wavelengths  $\lambda_{\text{abs}}$  (nm). Fluorescence maximum wavelengths  $\lambda_{\text{em}}$  (nm). Stokes shifts  $\Delta\nu_{ST}$  (cm<sup>-1</sup>). ; Cyclo: Cyclohexane. CCl<sub>4</sub>: Carbon tetrachloride. Bu<sub>2</sub>O: n-Dibutylether. Et<sub>2</sub>O: Diethyl etherethylic ether. BuOAc : n-Butylacetate. EtOAcAcOEt: Eethyl acetate. DCM: Ddichloromethane. DCE: 1.2-Ddichloroethane. ACN: Aacetoneitrile.

**Table S3.** Dielectric constant ( $\epsilon$ ), refractive index (n) and orientation polarizability ( $\Delta f^*$ ) of 11 solvents.

	Cyclohexane (Cyclo)	Carbon tetrachloride (CCl <sub>4</sub> )	n-Dibutylether (Bu <sub>2</sub> O)	Diethyl ether (Et <sub>2</sub> O)	Chloroform (CHCl <sub>3</sub> )	n-Butylacetate (BuOAc)
$\epsilon$	2.02	2.24	3.1	4.33	4.81	5.07
n	1.426	1.416	1.399	1.352	1.443	1.392
$\Delta f^*$	0.1,	0.118	0.196	0.251	0.251	0.269
	Ethylacetate (EtOAc)	Dichloromethane (DCM)	Dichloroethane (DCE)	Acetone	Acetonitrile (ACN)	
$\epsilon$	6.02	8.93	10.5	20.7	37.5	
n	1.372	1.424	1.445	1.359	1.344	
$\Delta f^*$	0.292	0.319	0.326	0.374	0.393	

## 2. Cyclic voltammetry data


Cyclic voltammetry (CV) data were acquired using a BAS 100 Potentiostat (Bioanalytical Systems) and a PC computer containing BAS100W software (v2.3). A three-electrode system with a Pt working electrode (diameter 1.6 mm), a Pt counter electrode and a Ag/AgCl (with a 3 M NaCl filling solution) reference electrode was used. (n-Bu)<sub>4</sub>NPF<sub>6</sub> (0.1 M in CH<sub>2</sub>Cl<sub>2</sub>) served as an inert electrolyte. Cyclic voltammograms were recorded at a scan rate of 100 mV s<sup>-1</sup> for solution of dyes at a concentration of *ca.* 10<sup>-3</sup> M. Ferrocene was used as an internal standard

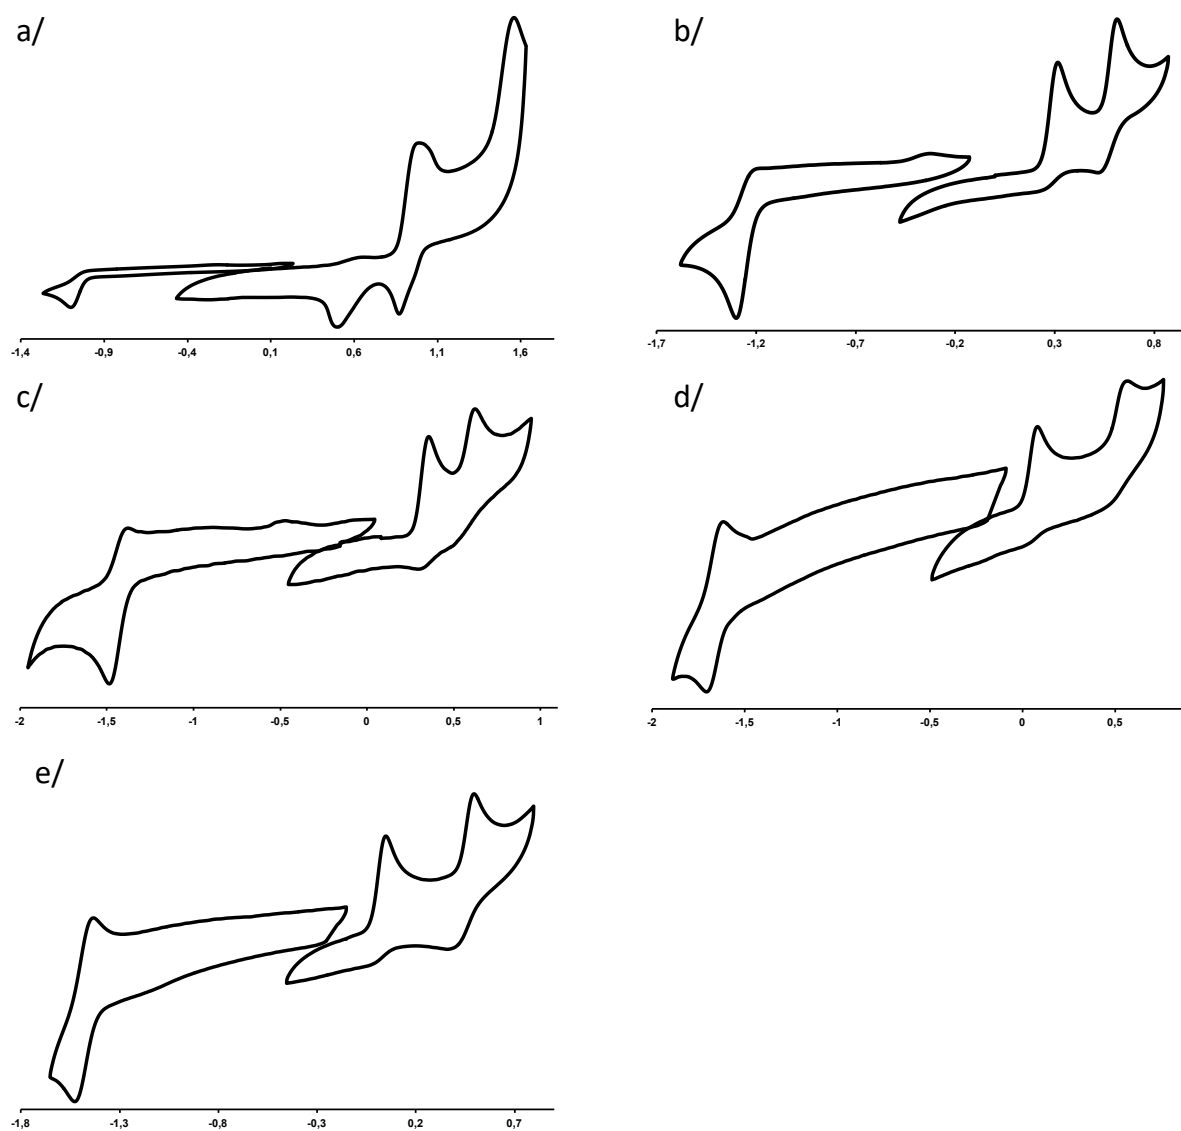

**Figure S1|** Cyclic voltammograms of **1** (a/), **3** (b/), **4** (c/), **5** (d/) and **6** (e/) in dichloromethane solution containing 0.1 M of (n-Bu)<sub>4</sub>NPF<sub>6</sub> (scan rate of 100 mV s<sup>-1</sup>).


### 3. Solvatochromism of polymethine model squaraine

Molecular structure of polymethine model squaraine is shown in Figure S2, named as compound 7.

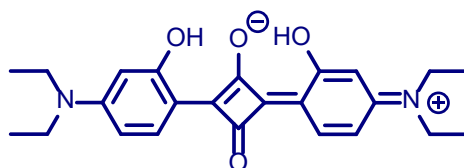


**Figure S2**| Molecular structure of polymethine model squaraine, compound 7.

Solvatochromism of compound 7 is shown in Figure S3.

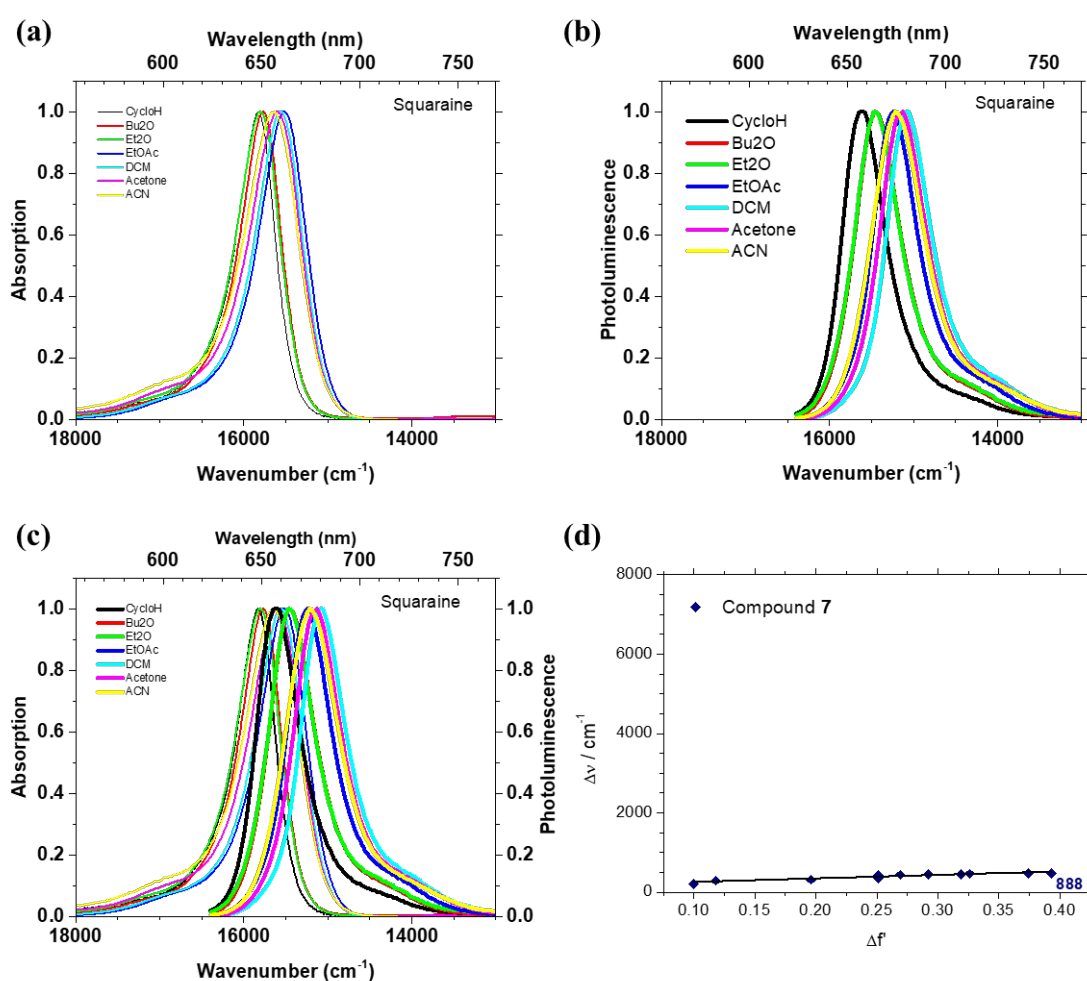

**Figure S3**| Solvatochromism of polymethine model squaraine 7. (a) and (b) show spectra of normalized absorption and normalized photoluminescence in 7 solvents with different polarity, namely, Cyclohexane (Cyclo), Bu<sub>2</sub>O (dibutyl ether), Diethyl ether (Et<sub>2</sub>O), Ethyl acetate (EtOAc), Dichloromethane (DCM), Acetone, Acetonitrile (ACN). (c) shows Stokes shift. (d) is the Lippert-Mataga plot of compound 7.


#### 4. Grazing incidence wide angle x-ray scattering (GIWAXS)

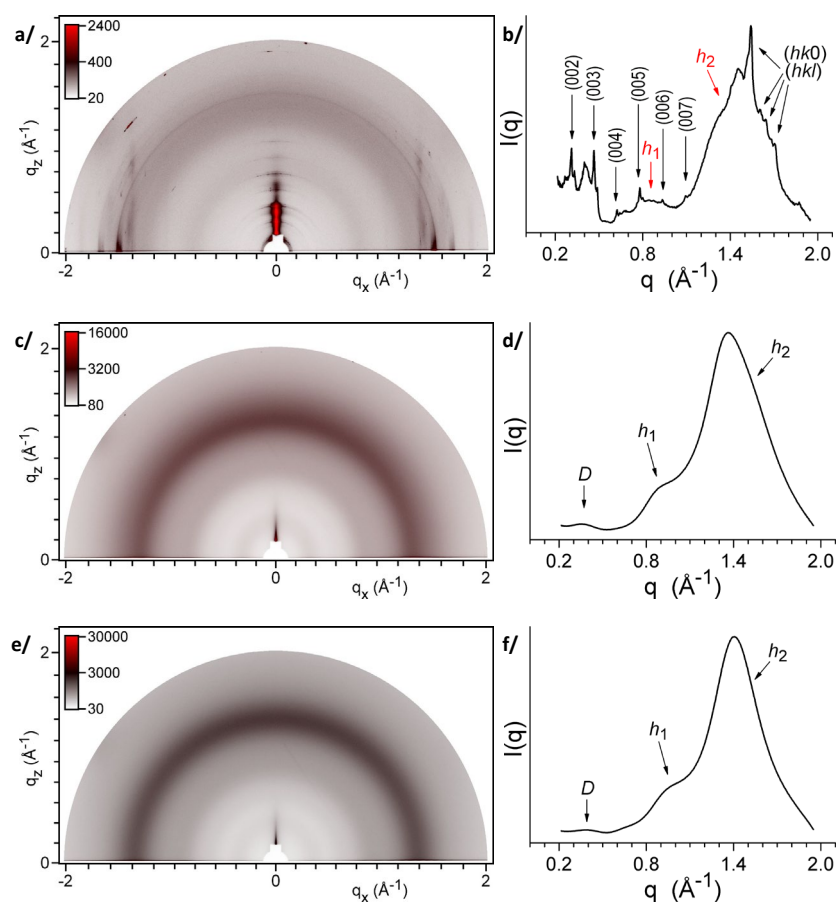

**Figure S4|** GIWAXS pattern (a/, c/ and e/) and the corresponding radial profile (b/, d/ and f/) of compound **1** (a/ and b/), **2** (c/ and d/) and **3** (e/ and f/).

The GIWAXS pattern (Fig S4 a/) and the corresponding radial profile (Fig S4 b/) of the pristine **1** film display coexistence of two phases: i) an amorphous phase (two broad scattering rings with maximums at  $q = 0.8$  and  $1.4 \text{ \AA}^{-1}$ , for average lateral distances  $h_1, h_2 = 2\pi/q = 7.8, 4.5 \text{ \AA}$ ) and ii) a lamellar crystalline phase (orders  $(00l)$  of the lamellar periodicity  $d = 40.5 \text{ \AA}$  and reflections  $(hk0)$  and  $(hkl)$  of the in-plane arrangement and the three-dimensional structure). There is naturally no orientation of amorphous domains, while the crystalline domains adopt orientations with lamellae parallel to substrate.

The GIWAXS pattern (Fig S4 c/) and the corresponding radial profile (Fig S4 d/) of the pristine **2** film reveal an amorphous film, giving rise to broad rings from lateral distances between segments ( $h_1, h_2 = 6.6, 4.5 \text{ \AA}$ ), and a broad small-angle ring from packing of entire molecules ( $D = 17 \text{ \AA}$ ). The GIWAXS pattern (Fig S4 e/) and the corresponding radial profile (Fig S4 f/) of the pristine **3** film reveal an amorphous film, giving rise to broad rings from lateral distances between segments ( $h_1, h_2 = 6.3, 4.5 \text{ \AA}$ ), and a broad small-angle ring from packing of entire molecules ( $D = 17 \text{ \AA}$ ).

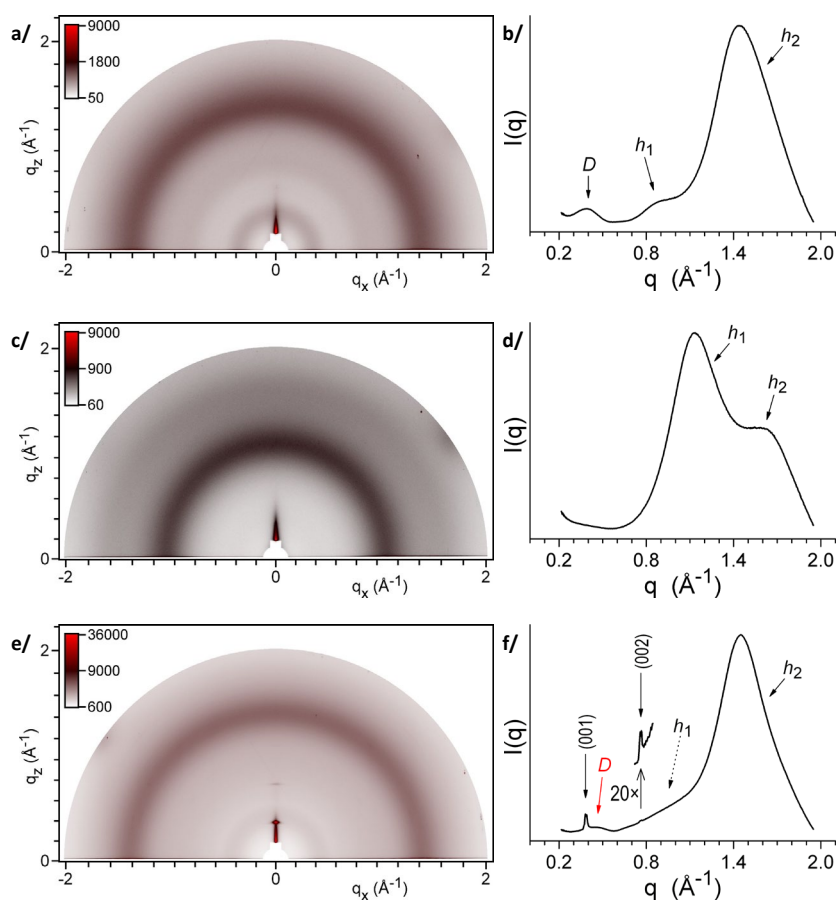

**Figure S5** | GIWAXS pattern (a/, c/ and e/) and the corresponding radial profile (b/, d/ and f/) of compound **4** (a/ and b/), **5** (c/ and d/) and **6** (e/ and f/).


The GIWAXS pattern (Fig S5 a/) and the corresponding radial profile (Fig S5 b/) of the pristine **4** film reveal an amorphous film, giving rise to broad rings from lateral distances between segments ( $h_1, h_2 = 6.6, 4.3 \text{ \AA}$ ), and a broad small-angle ring from packing of entire molecules ( $D = 16 \text{ \AA}$ ).

The GIWAXS pattern (Fig S5 c/) and the corresponding radial profile (Fig S5 d/) of the pristine **5** film reveal an amorphous film, giving rise to only two broad rings, with maximums at  $q = 1.1$  and  $1.6 \text{ \AA}^{-1}$  ( $h_1, h_2 = 5.6, 4.0 \text{ \AA}$ ) from lateral distances between molecular segments.


The GIWAXS pattern (Fig S5 e/) and the corresponding radial profile (Fig S5 f/) of the pristine **6** film display a smectic like structure with two sharp orders of a lamellar periodicity ( $d = 16.3 \text{ \AA}$ ) generated by the alternation of aliphatic chain and aromatic core layers, besides broad rings from liquid-like lateral distances within layers ( $h_2 = 4.3 \text{ \AA}$ ). The reflections align onto the meridian, which indicates that lamellae are oriented parallel to substrate. A continuous broad ring ( $D = 14 \text{ \AA}$ ) moreover appears in the small-angle region, due to the liquid-like molecular packing within amorphous domains that coexist with the mesomorphic domains.

## 5. Spectroscopic ellipsometry measurement

The alpha SE spectroscopic ellipsometer was used at incident angle  $70^\circ$  to measure  $\Psi$  and  $\Delta$  of the thin film from 380nm to 900nm. The rotating polarizer, photo-elastic modulator modulates between P-pol and S-pol from which the reflection ratio provides the information to unravel the dielectric index values of the thin films through Fresnel coefficient calculation. See Figure 5 for the dielectric permittivity spectra of all the six Curc series films. See Figures S6 for  $\Psi$  and  $\Delta$  measurement and fitted data. See Figure S7 for the refractive index  $n$  and absorption coefficient  $k$  of all the six Curc series films. Model fitting parameters of the measured data are shown in Table S4 to 11. Each film is fitted from a substrate/transparent thin film/air model. Fitting is conducted through the sum of oscillator functions such as Gaussian and Tauc-Lorentz oscillators.

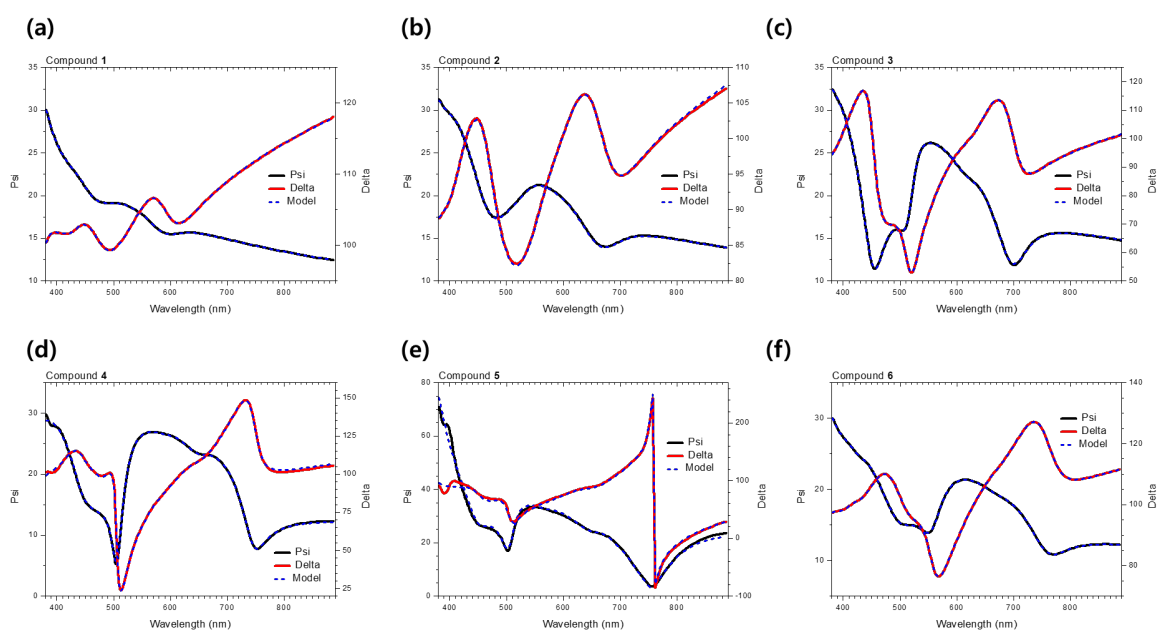

**Figure S6** | Measured  $\Psi$ , black, and  $\Delta$ , red, spectroscopic ellipsometry data and fitted model, dashed blue of six Curc series films.

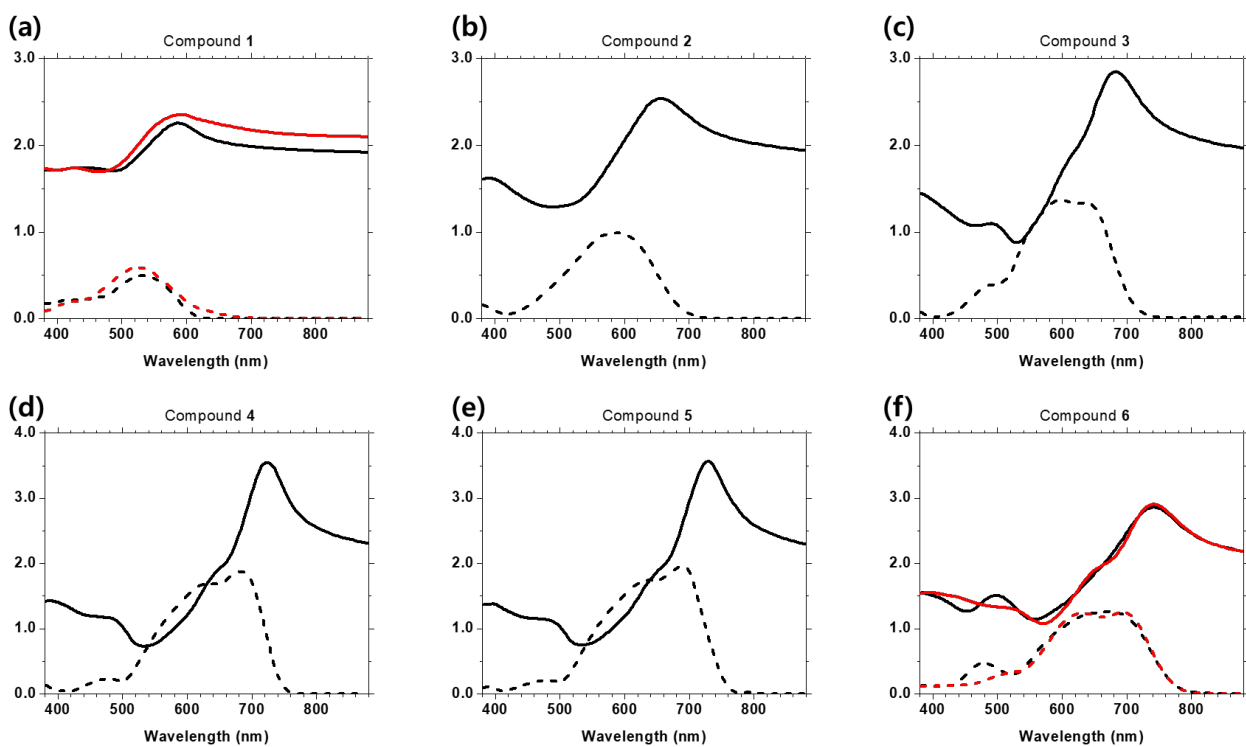

**Figure S7|** Refractive index  $n$  (solid curve) and absorption coefficient  $k$  (dashed curve) of all the six Curc series films are plotted. In (a) and (f) black and red curves correspond to ordinary and extra-ordinary components.

**Table S4.** Oscillator list for in-plane compound **1** dielectric permittivity

In-plane				
Number	Type	Amplitude	Broadening	Center energy
1	Gaussian	0.559	0.204	2.149
2	Gaussian	1.400	0.204	2.216
3	Gaussian	1.181	0.260	2.366
4	Gaussian	0.966	0.346	2.547
5	Gaussian	0.502	0.508	2.971
6	Gaussian	1.089	1.288	4.325



**Table S5.** Oscillator list for out-of-plane compound **1** dielectric permittivity

Out-of-plane				
Number	Type	Amplitude	Broadening	Center energy
1	Gaussian	0.523	0.208	2.150
2	Gaussian	1.421	0.195	2.193
3	Gaussian	1.258	0.257	2.361
4	Gaussian	0.975	0.330	2.531
5	Gaussian	0.572	0.608	2.923
6	Gaussian	0.550	0.576	3.823

**Table S6.** Oscillator list for compound **2** dielectric permittivity

Number	Type	Amplitude	Broadening	Center energy
1	Gaussian	2.410	0.206	1.957
2	Gaussian	2.539	0.268	2.102
3	Gaussian	1.268	0.323	2.269
4	Gaussian	0.798	0.409	2.508
5	Gaussian	0.569	0.499	3.338
6	Gaussian	0.076	0.228	2.806

**Table S7.** Oscillator list for compound **3** dielectric permittivity

Number	Type	Amplitude	Broadening	Center energy
1	Gaussian	4.043	0.152	1.873
2	Gaussian	4.632	0.274	2.028
3	Gaussian	1.187	0.208	2.241
4	Gaussian	0.655	0.339	2.488
5	Gaussian	0.435	0.377	3.444
6	Gaussian	0.268	0.417	2.662
7	Tauc-Lorentz	1.237	21.157	0.482

**Table S8.** Oscillator list for compound **4** dielectric permittivity

Number	Type	Amplitude	Broadening	Center energy
1	Gaussian	4.653	0.093	1.746
2	Gaussian	5.668	0.122	1.800
3	Gaussian	4.751	0.204	1.915
4	Gaussian	2.389	0.273	2.082
5	Gaussian	0.515	0.223	2.311
6	Gaussian	0.282	0.181	2.566
7	Gaussian	0.306	0.252	2.715
8	Gaussian	13.169	0.733	4.096
9	Tauc-Lorentz	32.099	0.088	1.690

**Table S9.** Oscillator list for compound **5** dielectric permittivity

Number	Type	Amplitude	Broadening	Center energy
1	Gaussian	4.670	0.093	1.726
2	Gaussian	6.101	0.123	1.787
3	Gaussian	5.068	0.243	1.911
4	Gaussian	1.718	0.339	2.125
5	Gaussian	0.338	0.259	2.626


**Table S10.** Oscillator list for in-plane compound **6** dielectric permittivity

In-plane				
Number	Type	Amplitude	Broadening	Center energy
1	Gaussian	1.316	0.122	1.695
2	Gaussian	2.590	0.157	1.756
3	Gaussian	3.467	0.260	1.859
4	Gaussian	2.089	0.353	2.066
5	Gaussian	1.150	0.323	2.570
6	Gaussian	0.413	2.034	3.589
7	Gaussian	47.977	0.025	0.024
9	Tauc-Lorentz	498.222	3.343	0.001

**Table S11.** Oscillator list for out-of-plane compound **6** dielectric permittivity

Out-of-plane				
Number	Type	Amplitude	Broadening	Center energy
1	Gaussian	2.408	0.146	1.715
2	Gaussian	3.008	0.160	1.755
3	Gaussian	3.023	0.218	1.894
4	Gaussian	2.175	0.277	2.027
5	Gaussian	0.653	0.371	2.335
6	Gaussian	0.365	0.460	2.587
7	Gaussian	0.071	0.173	2.867
8	Gaussian	0.390	0.567	3.158
9	Tauc-Lorentz	0.755	23.365	8.587

## 6. Reflection, transmission, absorption measurements and simulation data

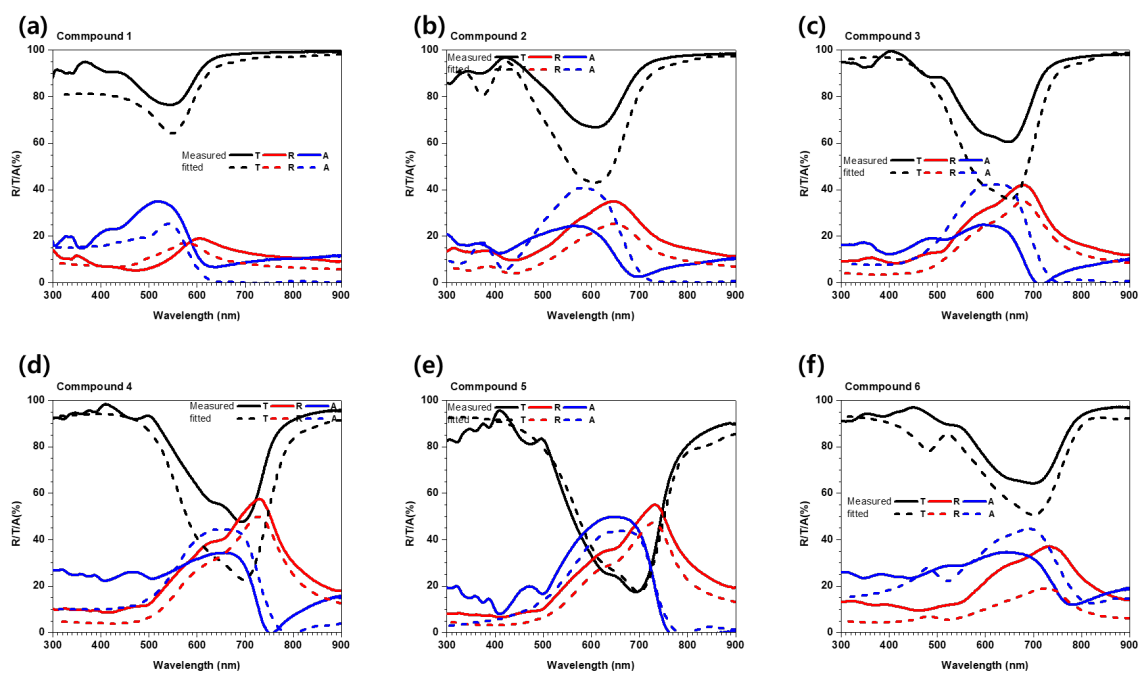

**Figure S8|** Measured data of six Curc series films (solid line) and simulated data (dashed line). Simulation data is obtained by use of dielectric permittivity spectrum of Figure 5.