



HAL
open science

Magnetically driven superhydrophobic/superoleophilic graphene-based polyurethane sponge for highly efficient oil/water separation and demulsification

A. Jamsaz, E.K. Goharshadi, Alexandre Barras, M. Ifires, Sabine Szunerits, Rabah Boukherroub

► **To cite this version:**

A. Jamsaz, E.K. Goharshadi, Alexandre Barras, M. Ifires, Sabine Szunerits, et al.. Magnetically driven superhydrophobic/superoleophilic graphene-based polyurethane sponge for highly efficient oil/water separation and demulsification. *Separation and Purification Technology*, 2021, 274, pp.118931. 10.1016/j.seppur.2021.118931 . hal-03546306

HAL Id: hal-03546306

<https://hal.science/hal-03546306v1>

Submitted on 25 Aug 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Magnetically driven superhydrophobic/superoleophilic graphene-based 1
polyurethane sponge for highly efficient oil/water separation and 2
demulsification 3

Azam Jamsaz^{a,b}, Elaheh K. Goharshadi^{a,c,*}, Alexandre Barras^b, Madjid Ifires^{b,d}, Sabine 5
Szunerits,^b Rabah Boukherroub^{b,*} 6

^a *Chemistry Department, Faculty of Science, Ferdowsi University of Mashhad, Mashhad* 9
9177948974, Iran 10

^b *Univ. Lille, CNRS, Centrale Lille, Univ. Polytechnique Hauts-de-France, UMR 8520 -* 11
IEMN, F-59000 Lille, France 12

^c *Nano Research Center, Ferdowsi University of Mashhad, Mashhad 9177948974, Iran* 13

^d *Research Center of Semi-conductor Technology for Energy, CRTSE - 02, Bd. Dr. Frantz* 14
FANON, B.P. 140 Algiers-7, Merveilles, 16038, Algeria 15

*Corresponding authors. 21

*E-mail: gohari@um.ac.ir (E. K. Goharshadi), rabah.boukherroub@univ-lille.fr (R. 22
Boukherroub) 23

Abstract 24

Cost-effective and efficient sorbents with emulsion-breaking capability, especially surfactant-stabilized emulsions, are required to remediate oil spills from water. Herein, *in situ* growth of magnetic $Mn_{0.01}Co_{0.90}Fe_3O_4$ (MCFO) nanoparticles (NPs) on reduced graphene oxide (RGO) was performed to prepare MCFO/RGO nanocomposite *via* a simple solvothermal method. The nanocomposite was coated onto a polyurethane (PU) sponge to fabricate a novel magnetic, superhydrophobic/superoleophilic and flame-retardant material. The prepared magnetic MCFO/RGO/PU was superhydrophobic with a contact angle of $165 \pm 1^\circ$. Compared with neat PU, the MCFO/RGO/PU sponge could be effectively driven by a magnet for oil collection in water. More importantly, the MCFO/RGO/PU sponge could effectively collect oil droplets from surfactant-free and stabilized toluene/water emulsions. In addition, the fabricated sponge exhibited excellent performance for oils and organic solvents sorption, achieving up to 131 times of its own weight and retaining its ability even after 10 sorption cycles. Interestingly, the thermal stability and fire retardancy of the prepared PU sponge were improved with respect to neat PU.

Keywords: $Mn_{0.01}Co_{0.90}Fe_3O_4$ /reduced graphene oxide; magnetic polyurethane sponge; superhydrophobic/superoleophilic; demulsification capacity; flame retardant

1. Introduction

48

Nowadays, the production of oily wastewater discharged from domestic and industrial activities is extremely increasing. Therefore, the separation of oil/water mixtures and treating oily wastewater resources have become an urgent world challenge. Generally, oil/water mixtures are classified into two categories including immiscible oil-water and miscible oil-water mixtures (oil-in-water (O/W) and water-in-oil (W/O) emulsions). Due to the small size ($d < 20 \mu m$) and high stability of emulsion droplets, their separation is more challenging and difficult than immiscible oil/water mixtures with average droplet size up to $150 \mu m$ [1]. As a result, much efforts have been devoted to design novel, low cost, reusable, and recyclable sorbents for oil/water separation.

The most common methods used for the separation of oil/water mixtures are sorption and filtration [2]. Nanocomposites, gels, powders, particles, and porous media are usually used as sorbent materials, while the common filtration materials applied in oil-water separation are films, filters, membranes, and meshes. Although filtration has been used as a successful method in industry, contaminants could not be effectively collected from mixtures. Sorbents, especially 3-dimensional (3D) porous materials, can easily adsorb contaminants from wastewater resources [3]. They are not expensive and there is no need of any specialized equipment to clean up the contaminants. Both natural including cotton fibers, kapok fibers, wool and synthetic sponges (e.g. polyurethane (PU) and melamine sponges), polystyrene fibers, and carbon nanotubes (CNTs) have been widely used as sorbents [2]. Although, natural materials offer some excellent advantages such as high abundance and low cost, they suffer from some shortcomings like flammability, non-reusability, introduction of new pollutants into the contaminated system, and poor sorption capacity. In addition, they are not suitable for separation of emulsified oil/water mixtures, especially in surfactant-stabilized emulsions [4]. In contrast, 3D porous sorbents like PU sponge with its specific features

represents an appealing alternative. PU sponge could act as a promising candidate for oil-water separation, because of its outstanding properties like large surface area, 3D skeleton, porous structure, remarkable flexibility, good sorption capacity, promising reusability, and inter-connected matrix [5-9]. Additionally, for effective oil/water separation, superhydrophobicity (surface with a water contact angle (WCA) higher than 150°) is crucial. Since PU is slightly hydrophobic, its non-wettability should be enhanced [10]. In addition, PU sponge is easily ignited and generates toxic gases [11]. These drawbacks hamper significantly the practical applications of PU sponge in oil-water separation [12]. Therefore, it is necessary to alter surface wettability of PU and make it suitable for oil/water separation processes such as emulsions (W/O and O/W) and highly viscous oil/water mixtures. There are several reports for the preparation of superhydrophobic/superoleophilic PU sponges. For example, Wang et al. [13] prepared a superhydrophobic and flame retardant PU sponge in an aqueous suspension containing alkaline water/ethanol, dopamine, fly ash, and dodecanethiol through the dip-coating method. The modified sponge presented a good oil sorption capacity (34-47 g/g) and separation efficiency for oil-in-water emulsions (93.0%).

To modify PU, graphene-based materials such as reduced graphene oxide (RGO) and graphene oxide (GO) have been utilized, owing to their remarkable physicochemical properties such as low density, large specific surface area, and biocompatibility [14, 15]. Moreover, GO sheets are decorated with hydrophilic functional groups including hydroxyl, epoxy, carbonyl, and carboxylic on their basal planes and edges. The oxygen-containing functional groups of GO can play a main role in modification of PU sponge. Liu et al. [16] synthesized silica NPs on GO surface (SiO₂/GO). Then, PU sponge was dipped into the ethanol/water solution containing the SiO₂/GO to obtain a hydrophobic SiO₂/GO/PU (WCA=145°). The modified PU sponge presented a high sorption capacity of 180 g/g for chloroform and exhibited a high stability for 10 cycles without any change of the intrinsic

structure of the PU sponge. Some of us [15] prepared a flame retardant, 98
superhydrophobic/superoleophilic graphene-based PU sponge by utilizing a simple *in-situ* 99
chemical method. The modified sponge displayed a high sorption capacity of 80 g/g for 100
chloroform and exhibited greater thermal stability with respect to neat PU. 101

By incorporation of magnetic nanoparticles (NPs) into graphene-based PU sponge, both 102
oil/water separation and fire retardancy properties could be enhanced [17-19]. Moreover, the 103
whole separation process could be controlled through external stimulation using a magnet. 104
Yang et al. [20] fabricated graphene aerogels modified by magnetic carbon nanospheres 105
through one-step hydrothermal *in-situ* electrostatic self-assembling method. The prepared 106
aerogels showed excellent thermal stability, flame retardancy, and magnetic properties. In 107
addition, they achieved high sorption capacity (187–537 g/g) for several organic solvents and 108
oils. Boukherroub et al. [21] prepared a superhydrophobic/superoleophilic PU sponge 109
through a two-step functionalization process. The modified sponge not only presented high 110
sorption capacity (40-75 g/g) for several oils, but it was also successfully applied for effective 111
separation of O/W emulsions. 112

Herein, we prepared $\text{Mn}_{0.01}\text{Co}_{0.90}\text{Fe}_3\text{O}_4$ nanoparticles (MCFO NPs) *via* a simple 113
solvothermal method. Then, the prepared NPs were grown on GO to form MCFO/RGO 114
nanocomposite and incorporated into a PU sponge. Introduction of some magnetic metal ions 115
such as manganese and cobalt ions can affect the thermal degradation and flame-retardancy 116
of PU [22]. To the best our knowledge, this is the first demonstration of the preparation of PU 117
functionalized with MCFO/RGO nanocomposite. The MCFO/RGO/PU sponge displayed 118
excellent superhydrophobic property with high selectivity and outstanding recyclability for 119
oil sorption. It could be magnetically directed to adsorb oils and organic solvents up to 131 120
times of its weight with respect to neat PU sponge. Additionally, one of the great success of 121
this work is to separate oil droplets from oil-in-water emulsions by the prepared 122

MCFO/RGO/PU sponge. In fact, oil/water emulsions especially in the presence of surfactants	123
are more difficult to separate in real spaces, as compared to immiscible oil/water mixtures.	124
2. Experimental	125
<i>2.1. Preparation of Mn_{0.01}Co_{0.90}Fe₃O₄ (MCFO)/RGO nanocomposite</i>	126
<i>In situ</i> growth of MCFO NPs on GO to produce MCFO/RGO nanocomposite was performed	127
by a facile solvothermal method. For this purpose, 80 mg of GO were dispersed in 80 mL of	128
ethylene glycol and 3 mL of ethyl acetate in an ultrasonic bath for 60 min. Afterwards,	129
Mn(CH ₃ COO) ₂ ·4H ₂ O (0.5 mmol), Co(CH ₃ COO) ₂ ·4H ₂ O (0.5 mmol), FeCl ₃ ·6H ₂ O (2.0 mmol),	130
and CH ₃ COONa (1.2 mmol) were added into the aforementioned mixture and sonicated to	131
form a homogeneous slurry. The mixture was sealed in a stainless-steel autoclave and heated	132
at 200 °C for 72 h. The obtained precipitate was collected by centrifugation and washed with	133
Milli-Q water and ethanol, and finally dried in an oven at 50 °C for 24 h to obtain the	134
MCFO/RGO nanocomposite. The similar procedure was used to prepare magnetic	135
MCFO/RGO nanocomposites with different amounts of GO (70, 80, and 90 mg). The	136
resulting nanocomposites are denoted as MCFO/RGO-1 (GO=70 mg), MCFO/RGO-2	137
(GO=80 mg), and MCFO/RGO-3 (GO=90 mg).	138
<i>2.2. Preparation of magnetic MCFO/RGO/PU sponge</i>	139
PU sponge pieces (1×1×1 cm ³) were washed first with acetone and then with DI water in an	140
ultrasonic bath for 10 min and dried in an oven for 2 h at 80 °C. The clean sponge was dipped	141
in a solution containing MCFO/RGO-1 (50 mg), ethanol (10 mL), and Milli-Q (10 mL) and	142
maintained under stirring for 6 h at room temperature. After that, the treated sponge was	143
dried by freeze-drying for 5 h. A similar approach was applied for the preparation of	144
MCFO/RGO-2 and 3 samples. Similarly, three sponges denoted as MCFO/RGO/PU-1	145

(GO=70 mg), MCFO/RGO/PU-2 (GO=80 mg) and MCFO/RGO/PU-3 (GO=90 mg) were prepared.

2.3. Preparation of RGO/PU sponge

GO (80 mg) was dispersed in water (80 mL) and sealed in a stainless-steel autoclave and heated at 200 °C for 72 h to prepare RGO powder. A clean PU sponge was dipped into the solution containing RGO (50 mg), ethanol (10 mL), and Milli-Q (10 mL) and maintained under stirring for 6 h at room temperature. Finally, the treated sponge was dried by freeze-drying for 5 h.

2.4. Oil and solvent sorption

The sorption capacity, Q , (mass/mass, g/g) of neat PU, RGO/PU, and MCFO/RGO/PU sponges for oils and organic solvents including cooked oil, chloroform, toluene, ethyl acetate, and dichloromethane was measured at room temperature. The sorption capacity was calculated using Eq. 1:

$$Q = \frac{m_1 - m_0}{m_0} \quad (1)$$

where m_0 and m_1 represent respectively the mass of MCFO/RGO/PU sponge before and after sorption.

2.5. Emulsion separation using MCFO/RGO/PU sponge

2.5.1. Surfactant-free water-in-oil emulsion (W/O)

Water (1 mL) was added to toluene (9 mL) and sonicated for 1 h to produce a milky white solution. The MCFO/RGO/PU sponge ($1 \times 1 \times 1 \text{ cm}^3$) was immersed in 4 mL of the emulsion for 30 min till the emulsion became colorless. The content of toluene in water was determined using a calibration curve generated from the UV-vis absorbance spectra at 260

nm of different concentrations of toluene dispersed in methanol/water (3/1, v/v) solution (see SI).
2.5.2. Surfactant-stabilized oil-in-water emulsion (O/W)
Pluronic F-127 (0.1 mg/mL in water) was added to toluene/water (1:9, v/v) and sonicated for 1 h to prepare a milky white solution. The MCFO/RGO/PU sponge (1×1×1 cm³) was immersed in 4 mL of the emulsion for 30 min till the emulsion became colorless. The content of toluene in water was determined as above.
3. Results and discussion
3.1. Preparation of magnetic superhydrophobic/superoleophilic (MCFO/RGO/PU) sponge
MCFO/RGO/PU sponge was fabricated through a two-step process including a solvothermal method to coat MCFO NPs on RGO nanosheets, followed by dip-coating method to load MCFO/RGO nanocomposite onto the PU surface. The preparation process of MCFO/RGO nanocomposite is illustrated in **Figure S1**. The well-dispersed GO nanosheets in ethylene glycol and ethyl acetate solution served as a substrate for the nucleation and *in situ* growth of MCFO NPs [23]. Co²⁺, Mn²⁺, and Fe³⁺ ions can be anchored on the GO surface during the nucleation process through electrostatic interactions between the positively charged metal ions and the negatively charged GO sheets [24, 25]. By elapsing time, GO was partially reduced to RGO and NPs were formed around the heterogeneous nucleation sites on the RGO sheets [26]. The solvents may act as structure-directing agents and prevent agglomeration of the NPs during the nucleation step. Finally, MCFO/RGO/PU nanocomposite was prepared by immersion of a PU sponge into a MCFO/RGO colloidal solution. ~~The sponge and nanocomposite were connected through hydrogen bonding between HNCO groups of PU and the deprotonated oxygen functional groups of MCFO/RGO. In addition, $\pi - \pi$ stacking interactions between RGO sheets and aromatic groups of PU sponge~~

could strengthen the bonding of MCFO/RGO nanocomposite on the PU surface. The MCFO 193
nanoparticles are strongly immobilized on the RGO surface owing to the presence of plenty 194
of oxygen-containing groups on the GO precursor. The MCFO/RGO is in turn adsorbed on 195
PU surface through π - π stacking interactions between RGO sheets and aromatic groups of 196
the PU sponge. 197

3.2. Characterization 198

3.2.1. WCA measurements 199

To investigate the wetting properties of neat PU and prepared sponges including 200
RGO/PU, MCFO/RGO/PU-1, MCFO/RGO/PU-2, and MCFO/RGO/PU-3, the WCA was 201
measured on three different locations on the surface of the sponges using 4 μ L of DI water 202
droplets at room temperature. As shown in **Figure 1**, neat PU sponge displays a WCA of 108 203
 $\pm 1^\circ$, which increased to $129 \pm 1^\circ$ after RGO coating. The hydrophobicity of the PU sponge 204
was enhanced upon loading MCFO/RGO on its surface, as witnessed by the apparent WCA 205
values of MCFO/RGO/PU-1 ($151 \pm 1^\circ$), MCFO/RGO/PU-2 ($165 \pm 1^\circ$) and MCFO/RGO/PU- 206
3 ($143 \pm 1^\circ$). It is obvious that the WCA of MCFO/RGO/PU-2 herein after named as 207
MCFO/RGO/PU is greater than those of other modified sponges. By increasing the amount of 208
GO above 80 mg, the WCA decreased. It is believed that higher amounts of GO can fill the 209
pores of the PU sponge and decrease its surface roughness and wettability. Also, it is likely 210
that RGO nanosheets are aggregated with increasing the amount of GO precursor. 211

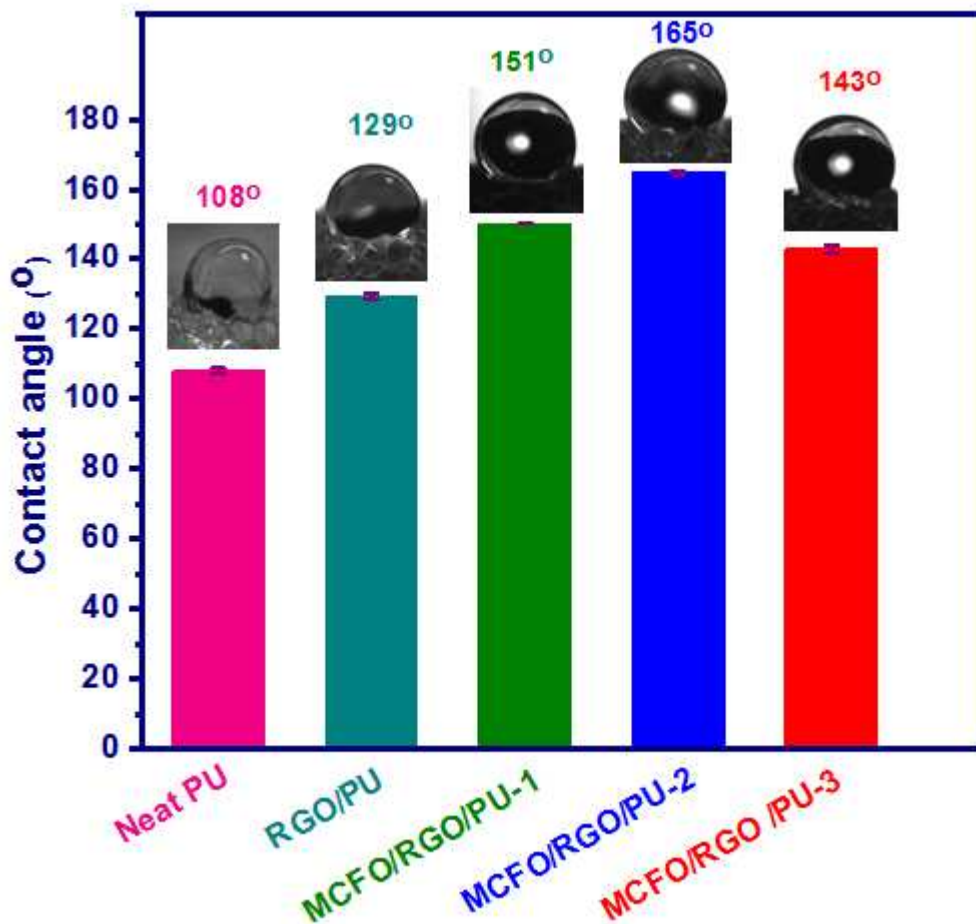


Figure 1. WCA values of neat PU and different MCFO/RGO/PU sponges.

To investigate the oleophilicity of MCFO/RGO/PU sponge, cooked oil was used. When cooked oil was dropped on the surface of the sponge, the oil droplet immediately spread out and meanwhile permeated into the porous structure of the sponge. Therefore, no contact angle could be measured, demonstrating the superoleophilicity of the MCFO/RGO/PU sponge (**Movie S1**). Owing to the superhydrophobicity and superoleophilicity of MCFO/RGO/PU sponge, it has a great potential for practical application in oil/water separation processes.

3.2.2. XRD, FTIR, Raman, XPS, and TEM analyses

The XRD patterns of GO and MCFO/RGO are depicted in **Figure S2**. The sharp peak at $2\theta=10.85^\circ$ in the XRD pattern of GO corresponds to the (002) crystalline plane with a large

interlayer distance of 8.2 Å due to the presence of oxygen containing functional groups. This peak disappears for MCFO/RGO nanocomposite, confirming the partial recovery of graphitic crystal structure. Indeed, two new peaks at 24.36° and 42.98° assigned respectively to the (002) and (102) crystalline planes of RGO appeared. The XRD pattern of MCFO/RGO comprises six characteristic diffraction peaks at $2\theta=18.48^\circ$, 30.06° , 35.55° , 53.86° , 56.95° , and 62.67° attributed respectively to the (111), (220), (311), (422), (511), and (440) lattice planes. These peaks indicate magnetite Fe_3O_4 phase formation (JCPDS-96-900-9770) [27]. The two peaks at $2\theta=44.50^\circ$ and 47.65° correspond respectively to the (002) and (101) crystalline planes of hcp-Co (JCPDS-96-901-0968) [28]. In addition, the peak at about $2\theta=42.98^\circ$ (400) (JCPDS-96-153-9040) is ascribed to cubic-Mn [29]. The atomic ratio of Mn and Co was calculated by ICP analysis. The presence of magnetite Fe_3O_4 phase and the atomic ratio of Co and Mn elements (0.90:0.01), determined from ICP analysis, suggest the formation of $\text{Mn}_{0.01}\text{Co}_{0.90}\text{Fe}_3\text{O}_4$.

The FTIR spectra of GO, RGO, and magnetic MCFO/RGO are displayed in **Figure S3**. The FTIR spectrum of GO shows bands at 3381, 1726, 1620, 1383, 1228, and 1054 cm^{-1} ascribed respectively to O-H, C=O carboxyl, C=C in the aromatic ring, C-OH, epoxy C-O, and alkoxy C-O vibrations. The FTIR spectrum of RGO exhibits four weak bands at 3381, 1726, 1582, and 1052 cm^{-1} assigned respectively to O-H, C=O carboxyl, C=C, and alkoxy C-O vibration modes [15]. The C=C stretching mode of RGO was blue-shifted from 1620 to 1582 cm^{-1} , suggesting an increased structural ordering and restoration of sp^2 domains due to hydrothermal reduction of GO [30]. The FTIR spectrum of MCFO/RGO is composed of bands at 3381, 1620, 1390, and 680 cm^{-1} assigned to vibrations of O-H, C=C in the aromatic ring, Fe-O stretching mode of Fe_3O_4 [31], and Co(III)-O, respectively [32]. The bands at 1040, 1172, and 1230 cm^{-1} are related to the interactions among Mn, OH, and O groups atoms/groups [33, 34].

Figure S4 displays the Raman spectrum of MCFO/RGO with four obvious peaks of RGO, 250
marked as D (1354 cm^{-1}), G (1586 cm^{-1}), 2D (2700 cm^{-1}), and D+G (2950 cm^{-1}) bands [35]. 251
The G band is related to E_{2g} vibration mode of sp^2 carbon domains, whereas the D band 252
arises from structural defects [36]. The 2D and D+G bands are due to the overtone of the D 253
band and the combination mode induced by disorder, respectively [37]. Also, the peaks at 254
around 663 and 672 cm^{-1} are characteristic of manganese oxide [38] and Fe_3O_4 NPs [39], 255
respectively. It is likely that both peaks are overlapped. The peak at 811 cm^{-1} is attributed to 256
cobalt oxide [40]. There is an extra peak at 960 cm^{-1} due to silicon [41]. 257

To assess the chemical composition, XPS analysis of MCFO/RGO nanocomposite was 258
performed. **Figure S5a** depicts the XPS survey spectrum of MCFO/RGO, comprising peaks 259
due to C 1s (285 eV), O 1s (532 eV), Mn 2p (642 eV), Fe 2p (710 eV), and Co 2p (781 eV), 260
which is in a good agreement with the composition of the material. The atomic percentage of 261
C 1s, O 1s, Co 2p, Fe 2p, and Mn 2p elements are 52.52, 32.75, 10.47, 3.77, and 0.49 at.%, 262
respectively. The C 1s core level spectrum can be deconvoluted into four peaks at binding 263
energies of 284.2, 285.1, 286.2, and 288.4 eV due to C=C, sp^3 C-C, epoxy and/or hydroxyl 264
(C-O/C-OH), and carboxyl (O-C=O) functional groups, respectively (**Figure S5b**). The O 1s 265
spectrum was curve-fitted with two peaks at binding energies of 531.5 and 532.8 eV assigned 266
to epoxy (C-O) and hydroxyl (C-OH) groups, respectively (**Figure S5c**). As shown in **Figure** 267
S5d, the high-resolution spectrum of the Mn 2p contains a pair of peaks located at about 268
 642.2 and 653.6 eV attributed respectively to Mn $2p_{3/2}$ and Mn $2p_{1/2}$. The Mn $2p_{3/2}$ peak is 269
deconvoluted into three peaks at 640.4 , 642.1 , and 643.5 eV related to Mn^{2+} , Mn^{3+} , and Mn^{4+} 270
valence states, respectively [42]. The Mn $2p_{1/2}$ peak can be fitted with three peaks at binding 271
energies of 651.1 , 652.7 , and 654.1 eV due to Mn^{2+} , Mn^{3+} and Mn^{4+} valence states, 272
respectively [42-44]. Also, two satellites are observed at 646.1 and 659.3 eV [42, 45]. The 273
Mn peak in the survey spectrum is weak, indicating that the content of Mn ions in 274

MCFO/RGO is low and Mn ions are doped into the interior of the nanocomposite. **Figure S5e** illustrates the Fe 2p XPS core level spectrum, which is deconvoluted in two main peaks including Fe 2p_{3/2} and Fe 2p_{1/2}. Fe 2p_{3/2} can be fitted with three peaks at binding energies of 705.2, 709.9, and 712.1 eV which are the characteristic peaks of Fe⁰, Fe²⁺, and Fe³⁺, respectively [46]. Fe 2p_{1/2} peak can be fitted with two peaks at 724.0 and 726.2 eV ascribed to Fe²⁺ and Fe³⁺, respectively [47]. Moreover, two satellite peaks are observed at 719.1 and 733.1 eV which are due to Fe³⁺ and Fe²⁺ chemical states present in Fe₃O₄ phase [48]. The high-resolution spectrum of the Co 2p in **Figure S5f** shows characteristic peaks of Co at about 781.3 eV (Co 2p_{3/2}) and 796.1 eV (Co 2p_{1/2}). The Co 2p_{3/2} spectrum can be deconvoluted into two peaks at 781.0 and 783.6 eV that are the characteristic peaks for Co³⁺ 2p_{3/2} and Co²⁺ 2p_{3/2}, respectively. In addition, the deconvolution of Co 2p_{1/2} shows two peaks at 796.2 and 798.4 eV which correspond to Co³⁺ 2p_{1/2} and Co³⁺ 2p_{1/2}, respectively. Also, two satellites are observed at 787.0 and 803.2 eV [49].

The TEM images of GO and MCFO/RGO nanocomposite are exhibited in **Figure S6**. The TEM of GO displays a characteristic crumpled surface. The TEM of MCFO/RGO shows the presence of MCFO nanospheres with a size of 3-6 nm attached onto RGO sheets.

3.2.3. XRD and FTIR of MCFO/RGO/PU sponge

The XRD patterns of neat PU and MCFO/RGO/PU sponges are depicted in **Figure S7**. The peak at $2\theta=20.7^\circ$ in the XRD pattern of neat PU corresponds to the (110) crystalline plane [50]. In addition, the characteristic peaks of MCFO/RGO nanocomposite and PU sponges are clearly observed in MCFO/RGO/PU sponge XRD pattern. A very strong broad amorphous peak at about $2\theta=20.7^\circ$ is ascribed to the (110) plane and related to the disordered structure of the PU matrix amorphous phase [51]. Besides, the observed diffraction peaks at 2θ values of 18.48° , 24.36° , 30.06° , 35.55° , 42.98° , 44.50° , 47.65° , 53.6° , 56.95° , and 62.67° corresponding respectively to the lattice planes of (111), (002), (220), (311), (400), (002),

(101), (422), (511), and (440) indicate that the MCFO/RGO nanocomposite was successfully loaded onto the PU sponge surface.

The FTIR spectra of neat PU and MCFO/RGO/PU sponges are displayed in **Figure S8**. The neat PU sponge shows some distinguished bands at 3270 cm^{-1} ($\nu_{\text{N-H}}$, $\nu_{\text{O-H}}$), $2850\text{--}2970$ ($\nu_{\text{C-H}}$, $-\text{CH}_3$ and $-\text{CH}_2$), 2271 cm^{-1} ($\nu_{\text{as-NCO}}$), 1722 cm^{-1} ($\nu_{\text{C=O}}$ in the amide), 1637 cm^{-1} ($\nu_{\text{C=O}}$ in the urea), 1529 cm^{-1} ($\nu_{\text{C=C}}$), 1445 cm^{-1} (C–H deformation), 1072 cm^{-1} ($\nu_{\text{C-O-C}}$), and 671 cm^{-1} (bending vibration of C–H) [52]. The FTIR spectrum of MCFO/RGO/PU sponge displays the same characteristic bands and positions like neat PU except for -NCO group. PU could form chemical bonds with materials through the NCO group of isocyanates. The absence of -NCO group in the FTIR spectrum of the modified PU sponge obviously demonstrates that the MCFO/RGO nanocomposite could be anchored on the PU surface effectively.

3.2.4. SEM images of neat PU, RGO/PU, MCFO/RGO/PU sponges

The SEM images of neat PU, RGO/PU, and magnetic MCFO/RGO/PU sponges are displayed in **Figure 2**. As shown in **Figure 2a**, the interconnected 3D porous structure of neat PU with a pore size ranging $100\text{--}500\text{ }\mu\text{m}$ makes it appropriate for sorption and storage of oil pollutants. Also, the smooth (absence of wrinkles) surface of the neat PU is obvious in its high magnification image (**Figure 2b**). As displayed in **Figure 2c** and **2d**, the surface of RGO/PU sponge exhibits higher roughness with respect to that of neat PU. From the SEM images in **Figure 2e** and **2f**, it is obvious that the MCFO/RGO/PU sponge maintains its porous structure with numerous tiny pores with respect to neat PU. It makes it appropriate for emulsion breakage. From the enlarged image of modified PU (**Figure 2g**), numerous irregular particles can be observed on the surface compared with the neat PU. This results in an enhancement of surface roughness and increase of superhydrophobic/superoleophilic property. In addition, compared with neat PU and RGO/PU sponges, such hierarchical

roughness could effectively reduce the diameter of sponge pores to the diameter of 325
toluene/water emulsion droplets' size. 326

The EDS spectrum of MCFO/RGO/PU sponge in **Figure S9** demonstrates the presence of 327
Co, Fe, Mn, O, and C elements in the modified sponge in good agreement with the XPS 328
analysis. 329


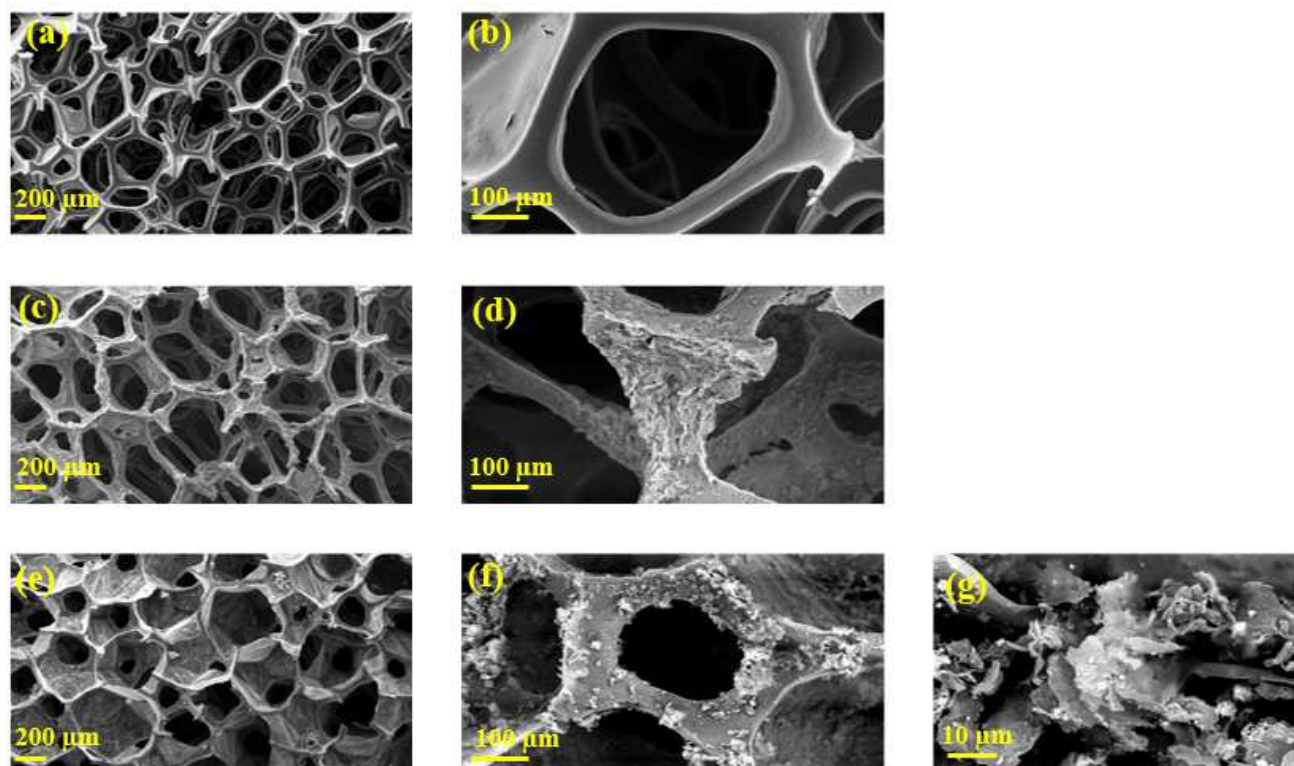


Figure 2. SEM images of (a-b) neat PU, (c-d) RGO/PU, and (e-g) MCFO/RGO/PU 331
sponges. 332


Magnetic properties 333

The magnetic curves of the MCFO/RGO nanocomposite and MCFO/RGO/PU sponge are 334
depicted in **Figure 3a**. The MCFO/RGO nanocomposite is ferromagnetic with remnant 335
magnetization, M_r , coercivity, H_c , and specific saturation magnetization, M_s , of 0.63 emu g^{-1} , 336
 20.0 Oe , and 22.05 emu g^{-1} , respectively. Also, the MCFO/RGO/PU sponge exhibited 337
ferromagnetic property with M_r , H_c , and M_s of 0.14 emu g^{-1} , 30.0 Oe , and 2.72 emu g^{-1} , 338
respectively. It is obvious that the magnetic property of MCFO/RGO/PU sponge is decreased 339

compared to that of MCFO/RGO nanocomposite due to the presence of relatively lower 340
magnetic content. Nevertheless, the magnetic properties of MCFO/RGO/PU sponge are 341
sufficient to manipulate the sponge using a magnet, as illustrated in **Figure 3b** and **movie S2**. 342
Figure 3c and **movie S3** show the magnetic response of MCFO/RGO/PU sponge. The 343
modified sponge can be easily driven to adsorb droplet of contaminant by using a magnet. 344

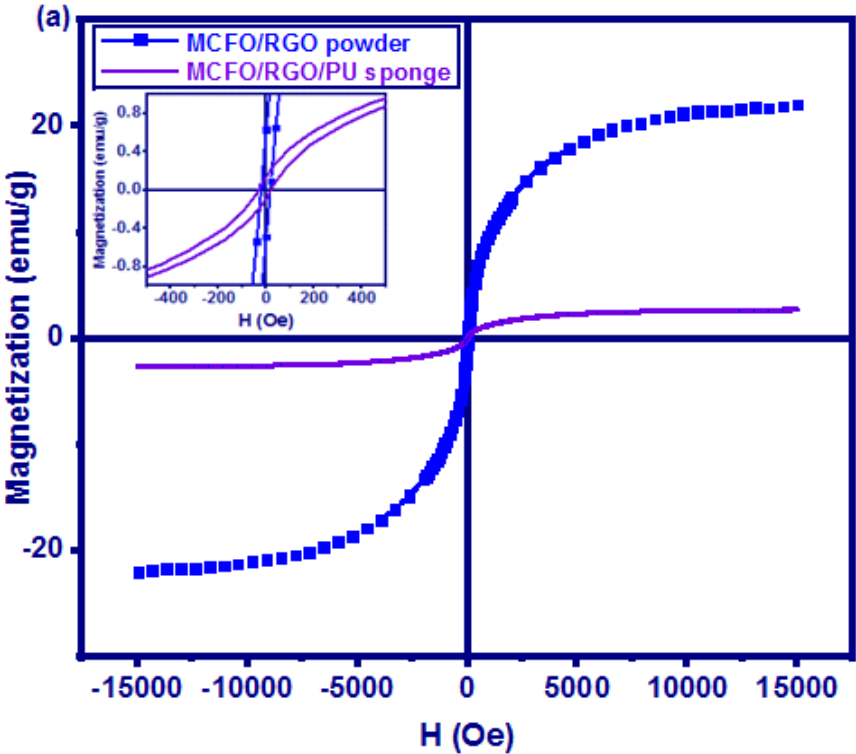

(b)

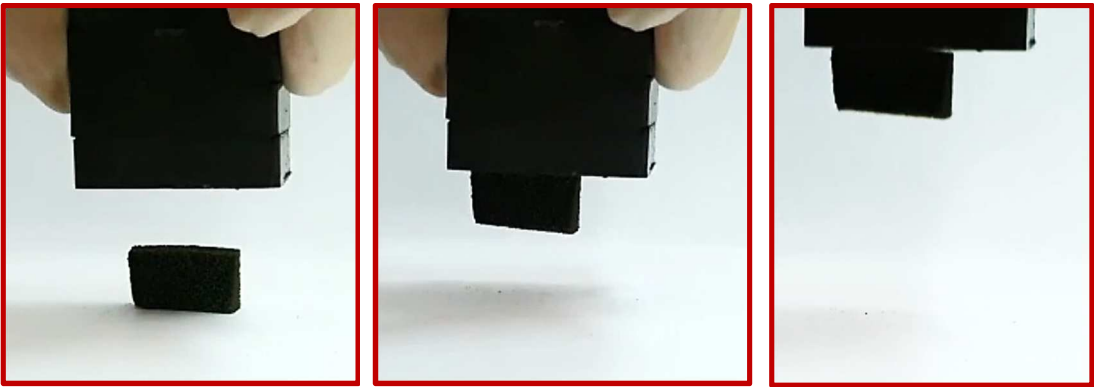

345

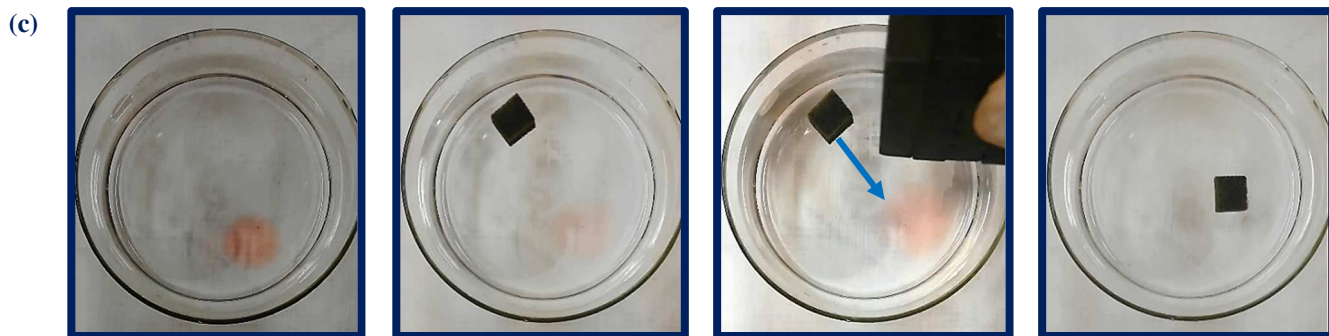


Figure 3. (a) Magnetization curves of MCFO/RGO nanocomposite and MCFO/RGO/PU 346
sponge, (b) lifting the modified sponge *via* a magnet bar, and (c) the removal process of 347
hydraulic oil by a piece of prepared sponge under a magnetic field. 348

3.4. MCFO/RGO/PU sponge stability in harsh conditions 349 350

Sorbent stability is an important factor in practical applications. **Figure S10a** confirms the 351
excellent stability of the magnetic MCFO/RGO/PU sponge in harsh conditions including 352
acidic, basic, and saline solutions upon immersion for 6 h at room temperature. In addition, 353
the excellent stability property of the modified sponge was examined in a wide range of 354
temperature from -4 to +140 °C. As shown in **Figure S10b**, the WCA is not significantly 355
impacted by increasing the temperature except at 140 °C where a slight decrease in the WCA 356
was observed (WCA=159±1°). Therefore, the results prove the chemical and thermal 357
stabilities of the modified MCFO/RGO/PU sponge, which guarantee its great potential for 358
practical applications. 359

3.5. Separation of oil/water mixtures using the MCFO/RGO/PU sponge 360

In order to demonstrate the oil/water separation performance of the magnetic 361
MCFO/RGO/PU sponge, a simple separation experiment was designed. The modified sponge 362
was embedded in a funnel and a mixture of methylene blue-dyed water and dichloromethane 363
was prepared and poured into the funnel (**Figure 4**). Although CH₂Cl₂ was successfully 364

separated from water by the sponge, organic solvents with lower density than water could not be easily separated. 365
366

367

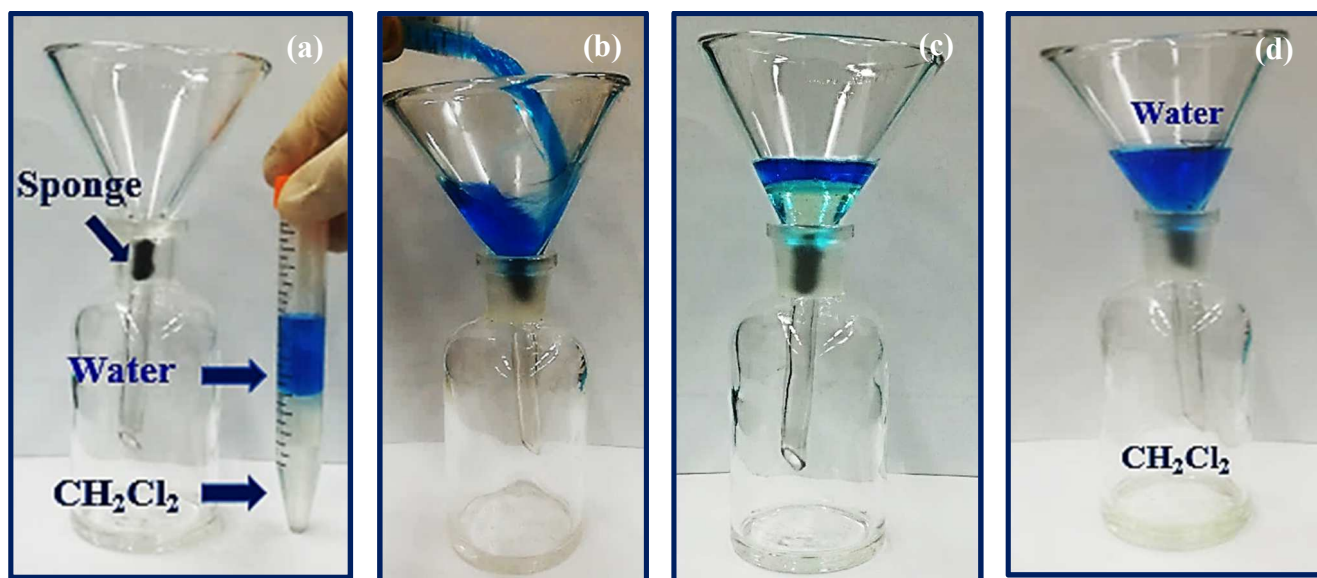


Figure 4. Snapshots of dichloromethane and colored water with methylene blue separation by MCFO/RGO/PU sponge. 368
369

The **movie S4** shows that the dichloromethane permeates through the MCFO/RGO/PU sponge rapidly, whereas the dyed water is maintained on top of the sponge, suggesting that the modified sponge has an excellent oil/water separation performance. 370
371
372

3.6. *Magnetic property maintenance of MCFO/RGO/PU sponge underwater* 373

To reveal the capability of magnetic response and oil/water separation of the MCFO/RGO/PU sponge, a methylene blue-dyed dichloromethane droplet is used as an oil spill underwater. As illustrated in **Figure 5**, the dichloromethane spill underwater could be rapidly adsorbed through an efficient magnetic drive by MCFO/RGO/PU sponge. Besides, the **movie S5** highlights that the functionalized sponge could effectively separate the oil droplet underwater and be handled by the magnet after oil sorption. 374
375
376
377
378
379

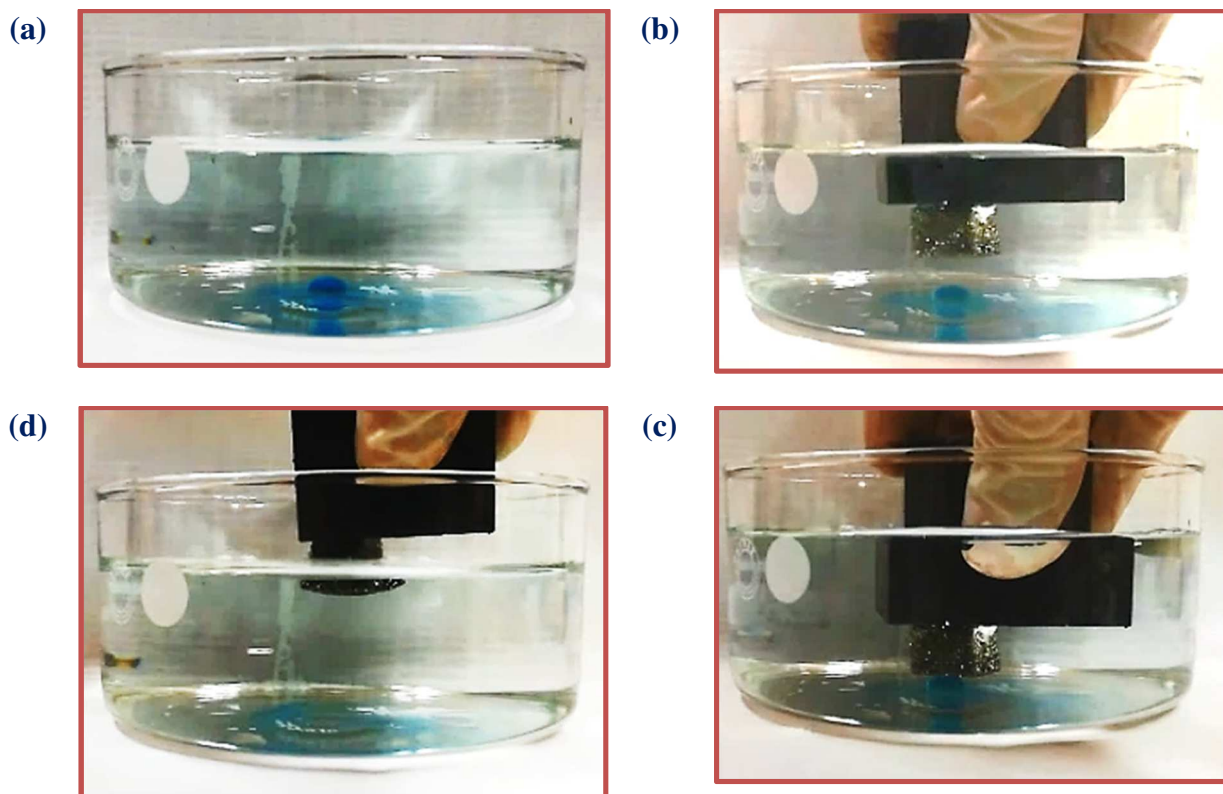


Figure 5. Snapshots of removal of methylene blue dyed underwater dichloromethane droplet 380
by the MCFO/RGO/PU sponge using a magnet. 381



3.7. Sorption capacity and recyclability 382

The sorption capacity of neat PU, RGO/PU, and magnetic MCFO/RGO/PU sponges for 384
oil and organic solvents including cooked oil, chloroform, ethyl acetate, toluene, and 385
dichloromethane was determined to be in the range of 4.4-88.5, 33.5-98.0, and 39.8-131.4 386
g/g, respectively (**Figure 6a**). Hence, MCFO/RGO/PU sponge exhibits the best performance 387
for sorption of oil and organic solvents due to the presence of several active sites on its 388
surface. The variation of the sorption capacity of the MCFO/RGO/PU sponge for organic 389
solvents and oils depends on their viscosity and density. The sorption capacity of RGO/PU 390
for oils and organic solvents is greater than that of neat PU, whereas it is lower than that of 391
MCFO/RGO/PU. Although RGO sheets enhance the hydrophobicity and oleophilicity of neat 392
PU, at the same time, they fill some pores of PU. The performance of MCFO/RGO/PU 393
sponge in comparison with other magnetic PU sponges is provided in **Table S1**. The 394

MCFO/RGO/PU prepared in this work has the greatest sorption capacity, which makes it as a promising sorbent for practical oil separation.

The recyclability of MCFO/RGO/PU sponge for five oil/organic solvents is investigated in **Figure 6b**. A simple mechanical squeezing method was used to desorb oils/organic solvents. The results showed that the MCFO/RGO/PU sponge could be recovered effectively, owing to its excellent mechanical property. The sorption capacity of MCFO/RGO/PU sponge did not change noticeably even after 10 sorption/desorption cycles (**Figure 6b**), which indicates its good structural stability.

XRD and SEM analysis of the MCFO/RGO/PU sponge after ten cycles of toluene sorption were performed. The XRD patterns of MCFO/RGO/PU sponge before and after ten sorption cycles of toluene are depicted in **Figure 6c**. The characteristic peaks of MCFO/RGO/PU sponge are clearly observed after ten sorption cycles, confirming the high stability of the sorbent. Besides, From the SEM images in **Figure 6d**, it is obvious that the MCFO/RGO/PU sponge maintained its porous structure after ten sorption cycles of toluene. In addition, from the enlarged images of the modified PU (**Figure 6e-g**), numerous irregular particles can be observed on the surface, indicating that the MCFO/RGO coating was not released from the PU surface after ten sorption cycles.

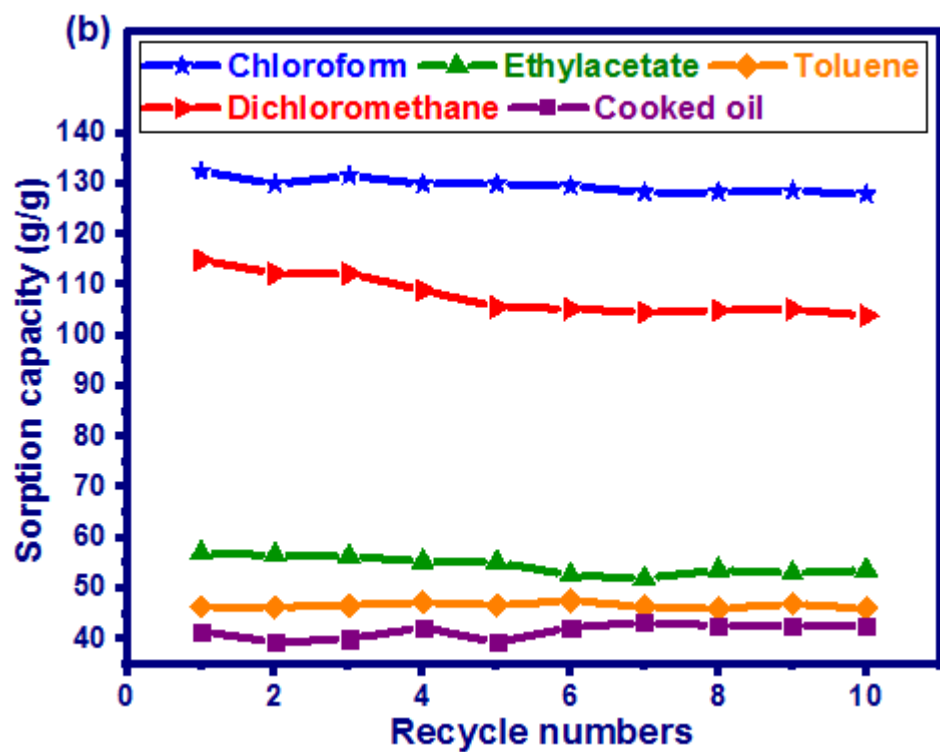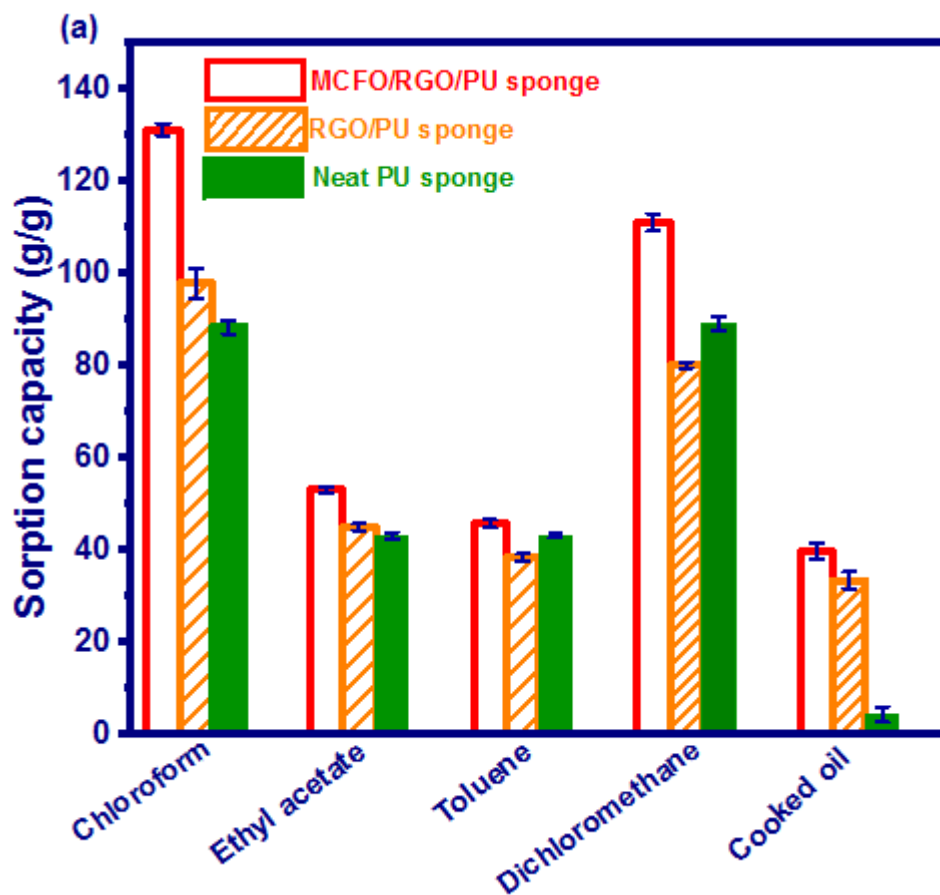



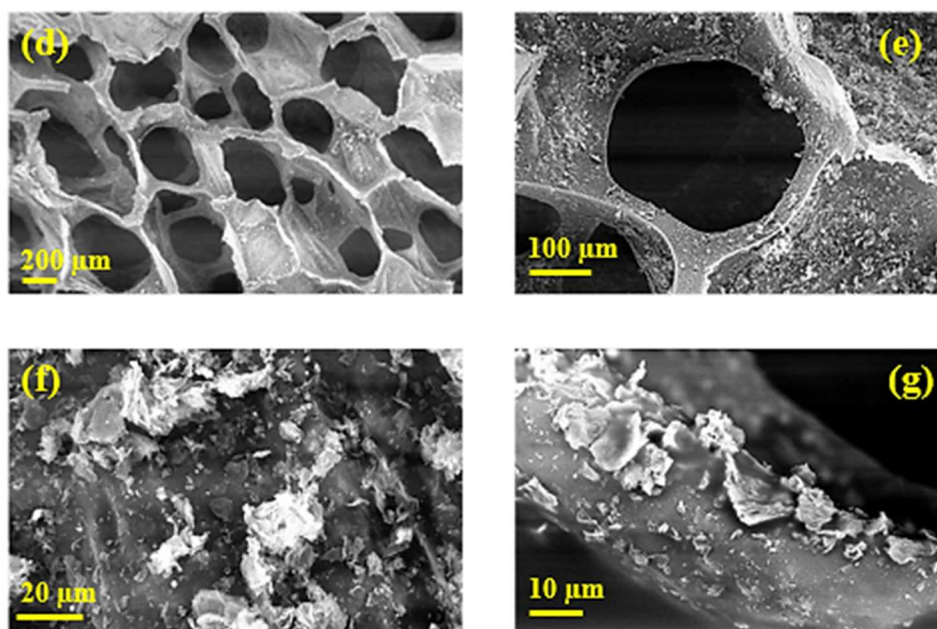


Figure 6. (a) The adsorption capacity of PU, RGO/PU, and MCFO/RGO/PU sponges for organic solvents and oils, (b) Recyclability of MCFO/RGO/PU for 10 adsorption cycles, (c) XRD patterns of MCFO/RGO/PU sponge before and after ten sorption cycles of toluene, and (d-g) SEM images of MCFO/RGO/PU sponge after ten sorption cycles of toluene.

3.8. Demulsification capacity of MCFO/RGO/PU sponge

The oil sewage, according to their diameter, d , can be classified into immiscible mixtures, unstable dispersions, and stable emulsions with $d < 20 \mu\text{m}$. The size mismatch between porous sponge (100-500 μm) and emulsified droplets limits the separation efficiency of sponges [1]. It is important to address this challenge while maintaining the high porosity of the sponges [19]. Herein, our strategy is to construct MCFO/RGO decorated PU surface, while preserving its intrinsic porous structure. As shown in SEM images (**Figure 2**), the MCFO/RGO nanocomposite could effectively reduce and match the diameter of sponge pores with that of toluene droplets in toluene/water emulsion. The MCFO/RGO/PU sponge could fully contact with emulsified water droplets, adsorb the toluene, and speed up the water coalescence. To investigate the demulsification ability of the MCFO/RGO/PU sponge, a W/O mixture was prepared by mixing 9 mL of toluene and 1 mL of water and sonicated for 1 h to produce a milky white colloid. In addition, O/W emulsion was prepared by addition of Pluronic F-127 (0.1 mg/mL in water) to toluene/water (1:9, v/v) and subsequently the mixture was emulsified under an ultrasonic bath for 1 h to prepare a milky white colloid. The MCFO/RGO/PU sponge was immersed in 4 mL emulsion until the emulsion became colorless. Before separation, the feeds of W/O and O/W mixtures were like a milky white liquid, as shown in **Figure 7a, b** left. After separation, the collected solutions were transparent compared to the feeds. The toluene content in the water phase was determined by UV-vis spectrophotometry (calibration curve in **Figure S11**). By immersion of the MCFO/RGO/PU sponge, a reduction in the toluene content (W/O) from 90% to 0.1% as well as (O/W) from 10% to 0.01% corresponding to toluene removal of 99.8% and 99.9%, respectively was achieved. It is worth to state that MCFO/RGO/PU sponge not only can separate the immiscible oil/water mixtures effectively, but it is also useful for emulsified oil/water mixtures especially in surfactant-stabilized emulsions.

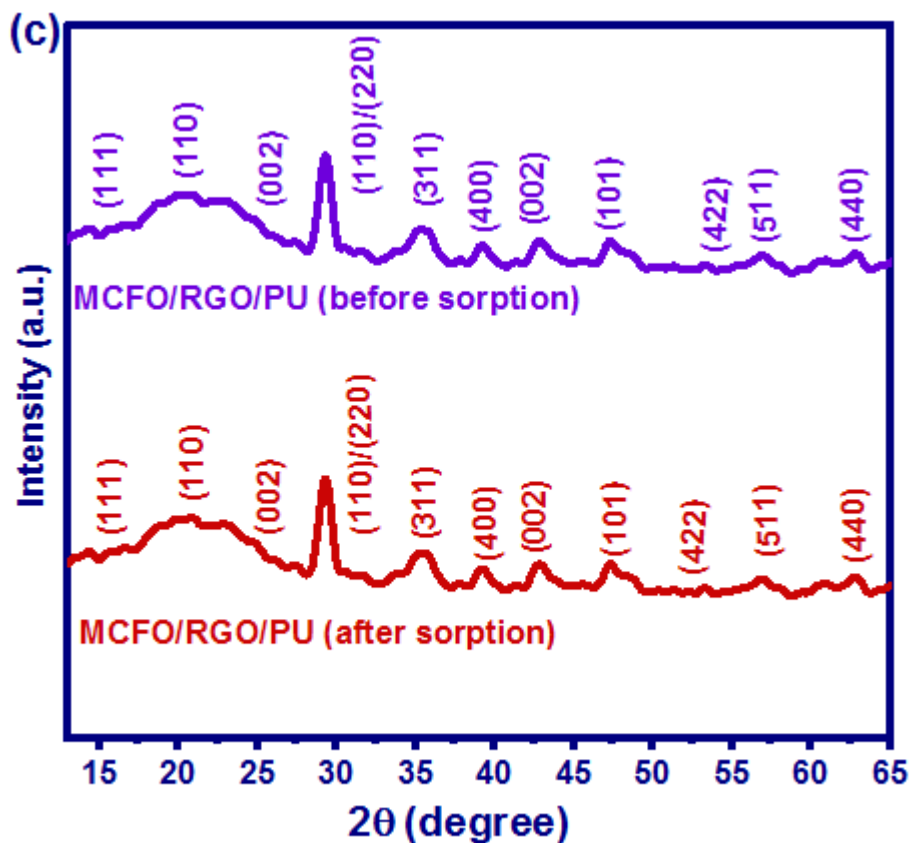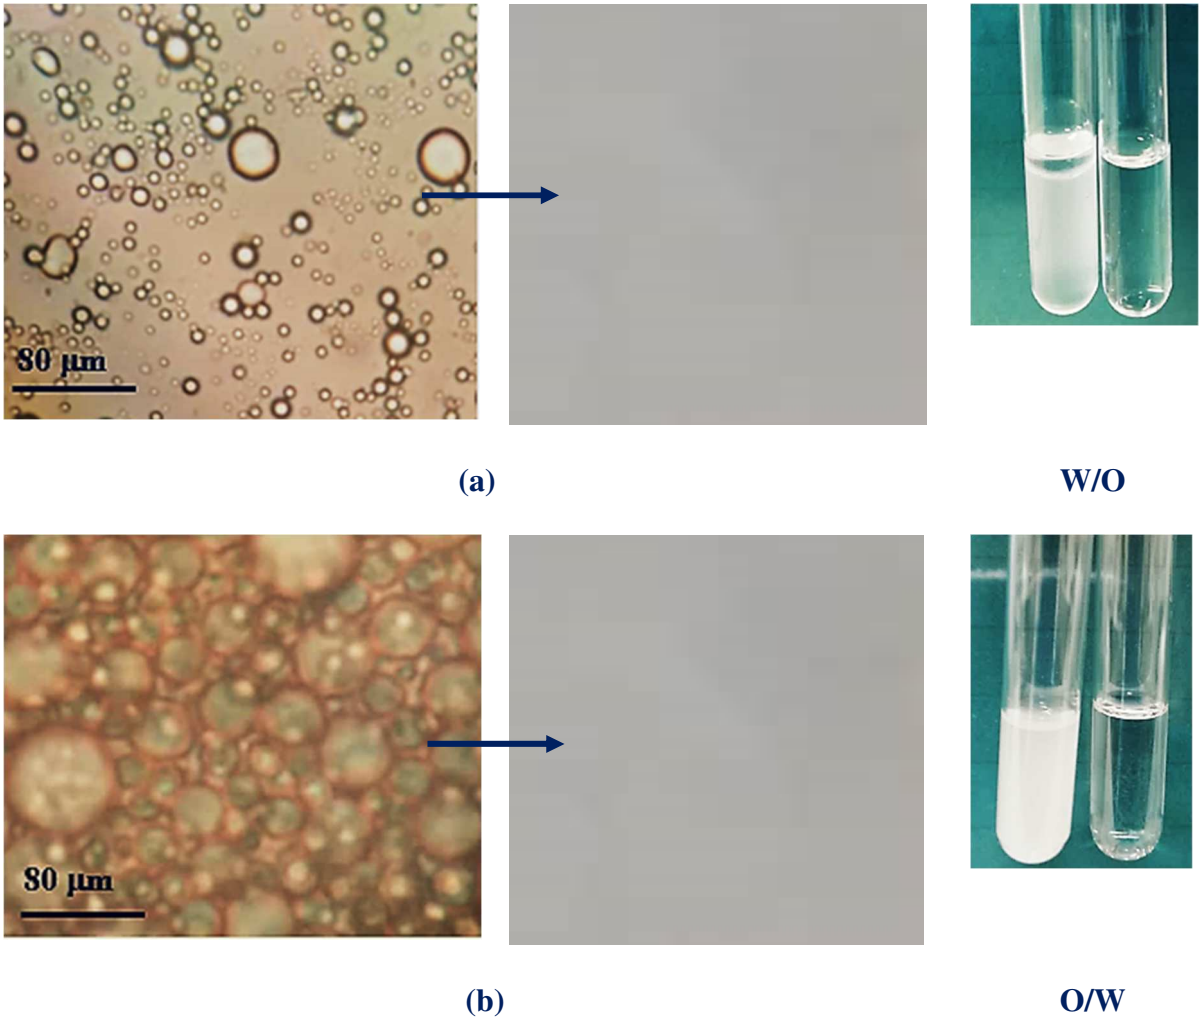

(a)

W/O

(b)

O/W

447 **Figure 7.** Optical photographs of surfactant-free water/toluene emulsion (W/O) and Pluronic
 448 F-127 emulsified toluene/water emulsion (O/W) (a) before and (b) after separation.

449
 450 *3.9. Surface energy estimate of MCFO/RGO/PU sponge*

451 Determining the free-energy of solid surfaces has been an elusive attempt for surface
 452 scientists. The surface energy can be measured by Fowkes, Owens–Wendt, Zisman, and
 453 Girifalco–Good–Fowkes (GGF) approaches [53].

454 **I. Fowkes theory**

455 The Fowkes equation is expressed as follows:

456
$$\gamma_L(1 + \cos \theta) = 2(\gamma_S^d \cdot \gamma_L^d)^{\frac{1}{2}} + 2(\gamma_S^p \cdot \gamma_L^p)^{\frac{1}{2}} \quad (2)$$

457 where θ is the contact angle of a liquid droplet on the solid surface, γ_L and γ_S refer
 458 respectively to surface energies of the liquid and solid calculated using Eq.3, d and h
 459 superscripts correspond to the dispersive and polar forces, respectively.

$$460 \quad \gamma_{L(S)} = \gamma_{L(S)}^d + \gamma_{L(S)}^p \quad (3)$$

461 In order to calculate the surface energy, polar and nonpolar liquids should be considered. The
 462 values of γ_L^d and γ_L^p can be obtained from the literature [54]. The surface energy of the
 463 magnetic MCFO/RGO/PU sponge was determined by testing different combinations
 464 including water/diiodomethane, water/hexadecane, glycerol/diiodomethane, and
 465 glycerol/hexadecane. The average contact angle values of 4 μ L liquid droplets are reported in
 466 **Table 1**. Upon substitution of these values into Eq. 2, two equations with two unknowns of
 467 γ_S^p and γ_S^d were solved. The surface energy, γ_S , of the magnetic MCFO/RGO/PU sponge was
 468 calculated as 48.36 mN·m⁻¹ ($\gamma_S^p = 9.16$ mN·m⁻¹ and $\gamma_S^d = 39.2$ mN·m⁻¹). The surface tension
 469 values of the polar and nonpolar liquids are exhibited in **Table 1**.

470 **Table 1.** Surface tension of various liquids and their corresponding contact angles (CAs) on
 471 the magnetic MCFO/RGO/PU sponge surface.

Liquid	γ_L^p /m N·m ⁻¹	γ_L^d /mN·m ⁻¹	γ_L /mN·m ⁻¹	CA ($\pm I^\circ$)
Water	51.0	21.8	72.8	165
Glycerol	26.4	37.0	63.4	92
DI Water +Ethanol (95/05%)	-	-	59.0	85
Formamide	18.7	39.5	58.2	84
DI Water +Ethanol (90/10%)	-	-	52.0	75
Ethylene-glycol	19.0	29.0	48.0	70
DI Water +Ethanol (85/15%)	-	-	46.0	66
DI Water +Ethanol (80/20%)	-	-	43.0	60
Ethanol	2.6	18.8	22.4	0
Diiodomethane	0.0	50.8	50.8	0
Hexadecane	0.0	27.6	27.6	0

Dodecane	0.0	25.4	25.4	0
Decan	0.0	23.8	23.8	0

472

473 II. Owens–Wendt theory

474 The Owens–Wendt theory or extended Fowkes equation:

$$475 \frac{\gamma_L(1 + \cos \theta)}{2 (\gamma_L^d)^{\frac{1}{2}}} = (\gamma_S^p)^{\frac{1}{2}} \frac{(\gamma_L^p)^{\frac{1}{2}}}{(\gamma_L^d)^{\frac{1}{2}}} + (\gamma_S^d)^{\frac{1}{2}} \quad (4)$$

476 The surface energy of the magnetic MCFO/RGO/PU sponge was determined by testing
 477 different combinations including water/diiodomethane, water/hexadecane,
 478 glycerol/diiodomethane, and glycerol/hexadecane. The surface energy, γ_S , of the magnetic
 479 MCFO/RGO/PU sponge was calculated as $49.4 \text{ mN}\cdot\text{m}^{-1}$ ($\gamma_S^p = 9.7 \text{ mN}\cdot\text{m}^{-1}$ and $\gamma_S^d = 39.7$
 480 $\text{mN}\cdot\text{m}^{-1}$).

481 III. Zisman model

482 The Zisman equation is expressed as follows:

$$483 \gamma_s = \frac{(b\gamma_c + 1)^2}{4b} \quad (5)$$

484 where, b is the slope of the fitted line.

485 **Figure S12** displays the linear fitting of data by the Zisman equation of $\cos \theta$ versus γ_L for
 486 liquids including glycerol, DI water + ethanol (95/05%), ethylene-glycol, DI water + ethanol
 487 (90/10%), DI water + ethanol (85/15%), DI water + ethanol (80/20%), and ethanol. The
 488 values of critical surface tension of wetting, γ_c , was obtained by extrapolating the linear curve
 489 to $\cos \theta = 1$. Finally, the surface energy, γ_S , of the magnetic MCFO/RGO/PU sponge was
 490 calculated using the Zisman equation ($23.5 \text{ mN}\cdot\text{m}^{-1}$).

491 IV. GGF theory

492 The GGF equation is expressed as follows:

$$\cos \theta = -1 + 2\left(\frac{\gamma_S^d}{\gamma_L}\right)^{\frac{1}{2}} \quad (6)$$

The γ_S^d of the magnetic MCFO/RGO/PU sponge was determined by testing alkane liquids including decane, dodecane, and hexadecane. The γ_S^d of the magnetic MCFO/RGO/PU sponge was calculated as 23.2 mN·m⁻¹.

These results clearly revealed that the Fowkes, Owens–Wendt, Zisman, and GGF methods are significantly dependent upon the choice of liquids for calculating the surface energy of a solid surface. In addition, Zisman method works well for nonpolar surfaces. Therefore, since the PU surface has some polar components, the surface energy calculated using the Zisman method is not accurate. Besides, the GGF and Zisman methods underestimate the dispersive component of the magnetic sponge.

The results indicate that the surface energy values, obtained from the Owens–Wendt and the Fowkes methods, are more accurate. In addition, it is obvious that the degree of wettability was mainly dependent on the surface tension of the liquids. Indeed, the contact angle of liquids increases and follows a linear relation with increasing the surface tension. As a result, the magnetic MCFO/RGO/PU sponge could extensively adsorb liquids with low surface tension and repel liquids especially water with high surface tension. On the other hand, although the degree of wettability was mainly dependent on the surface tension of the liquids, there are other factors that affect the WCA such as the liquid density. There is an obvious difference in density of ethylene glycol (1.11 g/cm³) and diiodomethane (3.32 g/cm³). Therefore, WCA does not follow a linear relationship with surface tension for these two liquids. The contact angle of ethylene glycol is 70° while that of diiodomethane is about 0°.

3.10. Flame retardancy

PU sponges generate a large extent of toxic gases like carbon monoxide and hydrogen cyanide. Their open-cell structure makes oxygen diffusing through the pores and provides

517 more combustion sites. Hence, it is challenging to produce a highly efficient flame retardant
518 (FR) barrier with sufficient thickness to strengthen PU sponges against flame [55]. Generally,
519 during the combustion of FRs, a charred layer is produced which can serve as a physical
520 barrier to hinder heat from underlayer substrates. Recently, graphene and its derivatives like
521 RGO have attracted much attention as FR to hinder the transfer of combustion gases into the
522 inflammable polymer skeleton [15]. Indeed, because of the large surface area and lamellar
523 structure of RGO, it is favorable to form a physical protective layer on the PU surface.
524 However, its low decomposition temperature (less than 600 °C) greatly restricts RGO
525 application as a fire retardant [56]. To address this issue, metal ions and metal oxides known
526 as non-intumescent flame-retardant materials are used to reinforce the fire retardancy property
527 of RGO. In addition, they can increase the compatibility of RGO with the PU skeleton [57]. In
528 this work, the neat PU and MCFO/RGO/PU sponges were cut into equal size, exposed to fire
529 and the combustion process was recorded. As shown in **Figure 8a**, the neat PU was ignited
530 immediately and burned completely within 13 s by leaving a small amount of residue at the
531 end of the test. Compared with neat PU sponge, the modified MCFO/RGO/PU sponge
532 exhibited self-extinguished and greater thermal stability properties brought by RGO and
533 $Mn_{0.01}Co_{0.90}Fe_3O_4$ content (**Figure 8b** and **Movie S5**).

534 **Figure S13** illustrates the FTIR spectra of MCFO/RGO/PU sponge before and after
535 burning. It is obvious that there is no significant change in the FTIR spectrum of
536 MCFO/RGO/PU sponge after burning test. Therefore, benefiting from the synergistic fire
537 retardancy of MCFO/RGO nanocomposite and PU sponge, the modified sponge revealed
538 remarkable adaptability in fire environments.

539

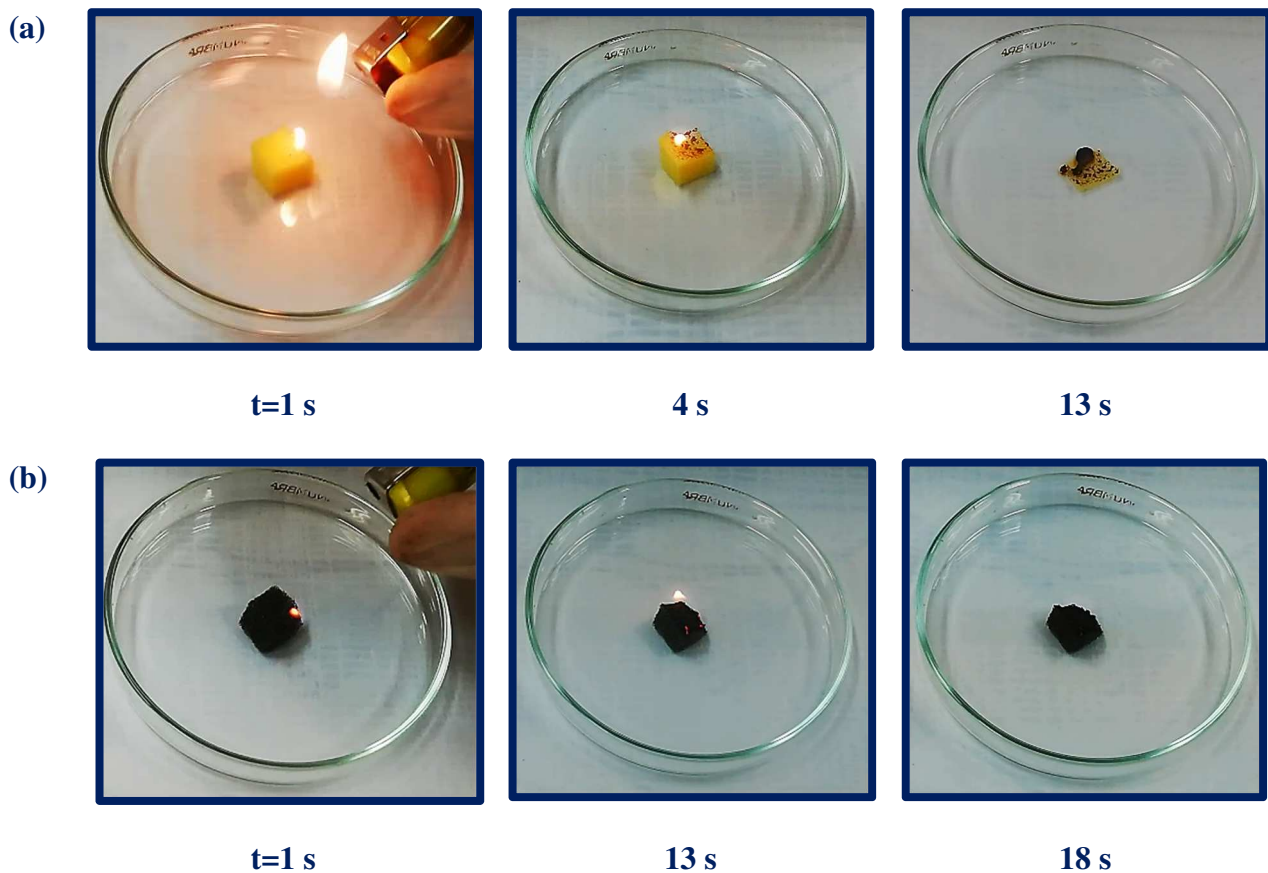


Figure 8. The snapshots of flammability test: (a) neat PU, (b) MCFO/RGO/PU sponges.

3.11. Mechanical stability of MCFO/RGO/PU sponge

The mechanical properties of MCFO/RGO/PU sponge are very important for practical applications in oil sorption. As shown in **Figure S14a-c**, water droplet still maintained a spherical shape under different mechanical deformation, including multiple times of substrate bending, compressing or twisting. The abrasion resistance of the MCFO/RGO/PU sponge (3×3×2 cm) was also examined. In this test, 200 g load was applied and the sponge was moved back/forth (an abrasion cycle) with abrasion length of about 5 cm. The WCA of the MCFO/RGO/PU sponge was recorded after various abrasion cycles. As shown in **Figure S15**, the WCA did not change obviously after every five abrasion cycles for a total of 20 cycles, indicating that the modified sponge possessed excellent superhydrophobicity and abrasion resistance. The insets in **Figure S15** show that the water droplets on MCFO/RGO/PU sponge still preserved a spherical shape with a WCA of 165°. This result confirmed that the

554 MCFO/RGO/PU sponge maintained its robust superhydrophobicity, because of the strong
555 adhesion of the MCFO/RGO nanocomposite on the PU sponge surface.

556 **4. Conclusion**

557 A magnetic, superhydrophobic/superoleophilic, and flame-retardant $Mn_{0.01}Co_{0.90}$
558 Fe_3O_4 /reduced graphene oxide/polyurethane (MCFO/RGO/PU) sponge was fabricated
559 through a simple dip-coating method. $Mn_{0.01}Co_{0.90}$ Fe_3O_4 /reduced graphene oxide
560 (MCFO/RGO) nanocomposite was synthesized through *in situ* growth of magnetic MCFO
561 nanoparticles on RGO *via* a solvothermal method. The nanocomposite decorated on PU
562 skeleton could increase effectively the surface roughness and change the sponge wettability.
563 The MCFO/RGO/PU sponge could be easily manipulated by a magnet and separate oil
564 droplets from surfactant-free and stabilized toluene/water emulsions. Also, it could adsorb oils
565 and organic solvents up to 131 times of its weight compared to neat PU sponge, while
566 retaining its ability even after 10 sorption cycles. Additionally, the MCFO/RGO/PU sponge
567 exhibited good mechanical and abrasion stability. Compared with neat PU, the robust
568 magnetic MCFO/RGO/PU sponge exhibits self-extinguished property due to the presence of
569 RGO in the nanocomposite anchored on PU matrix. The reported features make the modified
570 PU as a promising candidate for remediation of oil spills.

571 **Declaration of Competing Interest**

572 The authors declare that they have no known competing financial interests or personal
573 relationships that could have appeared to influence the work reported in this paper.

574 **Acknowledgements**

575 The authors would like to express their gratitude to Ferdowsi University of Mashhad for
576 support of this project (Grant no. 3/48779). The authors gratefully acknowledge financial
577 support from the Centre National de la Recherche Scientifique (CNRS), the University of
578 Lille, and the Hauts-de-France region. ICP analyses were performed in the « Spectrométrie

579 par torche à plasma » platform of the Research Federation Michel-Eugène Chevreul hosted by
580 the LASIRE laboratory.

581 **References**

582 [1] W. Zhang, N. Liu, Y. Cao, X. Lin, Y. Liu, L. Feng, Superwetting porous materials for
583 wastewater treatment: from immiscible oil/water mixture to emulsion separation, *Adv. Mater.*
584 *Interfaces* 4 (2017) 1600029-1600047 .

585 [2] R.K. Gupta, G.J. Dunderdale, M.W. England, A. Hozumi, Oil/water separation
586 techniques: a review of recent progresses and future directions, *J. Mater. Chem. A* 5 (2017)
587 16025-16058. [3] Y. Hou, Z. Wang, J. Guo, H. Shen, H. Zhang, N. Zhao, Y. Zhao, L. Chen,
588 S. Liang, Y. Jin, Facile fabrication of robust superhydrophobic porous materials and their
589 application in oil/water separation, *J. Mater. Chem. A* 3 (2015) 23252-23260.

590 [4] A. Laborel-Préneron, C. Magniont, J.-E. Aubert, Characterization of barley straw, hemp
591 shiv and corn cob as resources for bioaggregate based building materials, *Waste Biomass*
592 *Valorization* 9 (2018) 1095-1112 .

593 [5] M. Vintu, G. Unnikrishnan, Indolocarbazole based polymer coated super adsorbent
594 polyurethane sponges for oil/organic solvent removal, *J. Environ. Manage.* 248 (2019)
595 109344-109355.

596 [6] M. Khosravi, S. Azizian, Synthesis of a novel highly oleophilic and highly hydrophobic
597 sponge for rapid oil spill cleanup, *ACS Appl. Mater. Interfaces* 7 (2015) 25326-25333.

598 [7] Q. Zhu, Y. Chu, Z. Wang, N. Chen, L. Lin, F. Liu, Q. Pan, Robust superhydrophobic
599 polyurethane sponge as a highly reusable oil-absorption material, *J. Mater. Chem. A* 1 (2013)
600 5386-5393.

601 [8] B. Ge, Z. Zhang, X. Zhu, X. Men, X. Zhou, A superhydrophobic/superoleophilic sponge
602 for the selective absorption oil pollutants from water, *Colloids Surf., A* 457 (2014) 397-401.

- 603 [9] N. Cao, B. Yang, A. Barras, S. Szunerits, R. Boukherroub, Polyurethane sponge
604 functionalized with superhydrophobic nanodiamond particles for efficient oil/water
605 separation, *Chem. Eng. J.* 307 (2017) 319-325.
- 606 [10] Y. Tang, H. Huang, X. Guo, C. Zhong, Superhydrophobic Ether-Based Porous Organic
607 Polymer-Coated Polyurethane Sponge for Highly Efficient Oil–Water Separation, *Ind. Eng.*
608 *Chem. Res.* 59 (2020) 13228-13238.
- 609 [11] A. Andersson, A. Magnusson, S. Troedsson, S. Lundmark, F.H. Maurer, Intumescent
610 foams - a novel flame retardant system for flexible polyurethane foams, *J. Appl. Polym. Sci.*
611 109 (2008) 2269-2274.
- 612 [12] F. Zhou, T. Zhang, B. Zou, W. Hu, B. Wang, J. Zhan, C. Ma, Y. Hu, Synthesis of a novel
613 liquid phosphorus-containing flame retardant for flexible polyurethane foam: Combustion
614 behaviors and thermal properties, *Polym. Degrad. Stab.* 171 (2020) 109029-109065.
- 615 [13] J. Wang, H. Wang, G. Geng, Flame-retardant superhydrophobic coating derived from fly
616 ash on polymeric foam for efficient oil/corrosive water and emulsion separation, *J. Colloid*
617 *Interface Sci.* 525 (2018) 11-20.
- 618 [14] N. Yousefi, X. Lu, M. Elimelech, N. Tufenkji, Environmental performance of graphene-
619 based 3D macrostructures, *Nature Nanotechnol.* 14 (2019) 107-119.
- 620 [15] A. Jamsaz, E.K. Goharshadi, Flame retardant, superhydrophobic, and superoleophilic
621 reduced graphene oxide/orthoaminophenol polyurethane sponge for efficient oil/water
622 separation, *J. Mol. Liq.* 307 (2020) 112979-112991.
- 623 [16] X. Lü, Z. Cui, W. Wei, J. Xie, L. Jiang, J. Huang, J. Liu, Constructing polyurethane
624 sponge modified with silica/graphene oxide nanohybrids as a ternary sorbent, *Chem. Eng. J.*
625 284 (2016) 478-486.
- 626 [17] N. Chen, Q. Pan, Versatile fabrication of ultralight magnetic foams and application for
627 oil–water separation, *ACS nano* 7 (2013) 6875-6883.

628 [18] T. Yu, F. Halouane, D. Mathias, A. Barras, Z. Wang, A. Lv, S. Lu, W. Xu, D. Meziane,
629 N. Tiercelin, Preparation of magnetic, superhydrophobic/superoleophilic polyurethane
630 sponge: Separation of oil/water mixture and demulsification, *Chem. Eng. J.* 384 (2020)
631 123339-123348.

632 [19] Y. Liu ,X. Wang, S. Feng, Nonflammable and magnetic sponge decorated with
633 polydimethylsiloxane brush for multitasking and highly efficient oil–water separation, *Adv.*
634 *Funct. Mater.* 29 (2019) 1902488-1902500.

635 [20] W. Kang, Y. Cui, L. Qin, Y. Yang, Z. Zhao, X. Wang, X. Liu, A novel robust adsorbent
636 for efficient oil/water separation: Magnetic carbon nanospheres/graphene composite aerogel,
637 *J. Hazard. Mater.* 392 (2020) 122499-122512.

638 [21] O. Guselnikova, A. Barras, A. Addad, E. Sviridova, S. Szunerits, P. Postnikov, R.
639 Boukherroub, Magnetic polyurethane sponge for efficient oil adsorption and separation of oil
640 from oil-in-water emulsions, *Sep. Purif. Technol.* 240 (2020) 116627-116625.

641 [22] Y. Liu, J.-C. Zhao, C.-J. Zhang, Y. Guo, P. Zhu, D.-Y. Wang, Effect of manganese and
642 cobalt ions on flame retardancy and thermal degradation of bio-based alginate films, *J. Mater.*
643 *Sci.* 51 (2016) 1052-1065.

644 [23] H. Wang, J.T. Robinson, G. Diankov, H. Dai ,Nanocrystal growth on graphene with
645 various degrees of oxidation, *J. Am. Chem. Soc.* 132 (2010) 3270-3271.

646 [24] C. Peng, B. Chen, Y. Qin, S. Yang, C. Li, Y. Zuo, S. Liu, J. Yang, Facile ultrasonic
647 synthesis of CoO quantum dot/graphene nanosheet composites with high lithium storage
648 capacity, *ACS nano* 6 (2012) 1074-1081

649 [25] R. Zan, U. Bangert, Q. Ramasse, K.S. Novoselov, Metal– graphene interaction studied
650 via atomic resolution scanning transmission electron microscopy, *Nano Lett.* 11 (2011) 1087-
651 1092.

652 [26] Z. Zhang, Y. Wang, D. Li, Q. Tan, Y. Chen, Z. Zhong, F. Su, Mesoporous $Mn_{0.5}Co_{0.5}Fe_2O_4$ nanospheres grown on graphene for enhanced lithium storage properties, *Ind. Eng. Chem. Res.* 52 (2013) 14906-14912.

653
654

655 [27] H. El Ghandour, H. Zidan, M.M. Khalil, M. Ismail, Synthesis and some physical
656 properties of magnetite (Fe_3O_4) nanoparticles, *Int. J. Electrochem. Sci* 7 (2012) 5734-5745.

657 [28] M.A. Kashi, M. Ghaffari, F. Torshizi, Structural and magnetic tunability of Co/Cu
658 multilayer nanowires induced by electrolyte acidity and spacer layer thickness, *J. Alloys
659 Compd.* 820 (2020) 153087-153099.

660 [29] X. Zhu, H. Zhao, X. Niu, T. Liu, L. Shi, M. Lan, A comparative study of carbon
661 nanotube supported MFe_2O_4 spinels (M= Fe, Co, Mn) for amperometric determination of
662 H_2O_2 at neutral pH values, *Microchim. Acta* 183 (2016) 2431-2439.

663 [30] P. Bansal, A. Panwar, D. Bahadur, Effect of reaction temperature on structural and
664 optical properties of reduced graphene oxide, *Int. J. Mater., Mech. Manuf.* 2 (2014) 18-20.

665 [31] D.V. Quy, N.M. Hieu, P.T. Tra, N.H. Nam, N.H. Hai, N. Thai Son, P.T. Nghia, N.T.V.
666 Anh, T.T. Hong, N.H. Luong, Synthesis of silica-coated magnetic nanoparticles and
667 application in the detection of pathogenic viruses, *J. Nanomater.* 2013 (2013) 603940-603946.

668 [32] E.A. Aboelazm, G.A. Ali, K.F. Chong, Cobalt oxide supercapacitor electrode recovered
669 from spent lithium-ion battery, *Chem. Adv. Mater.* 3 (2018) 67-74.

670 [33] M. Mylarappa, V.V. Lakshmi, K.V. Mahesh, H. Nagaswarupa, N. Raghavendra, A facile
671 hydrothermal recovery of nano sealed MnO_2 particle from waste batteries: An advanced
672 material for electrochemical and environmental applications, *IOP Conf. Series: Materials
673 Science and Engineering*, 149 (2016) 12178-12188.

674 [34] R. Ali, S. Adil, A. Al-warthan, M.R.H. Siddiqui, Identification of active phase for
675 selective oxidation of benzyl alcohol with molecular oxygen catalyzed by copper-manganese
676 oxide nanoparticles, *J. Chem.* 2013 (2013) 367261-367269.

677 [35] S. Gupta, J. Narayan, Non-equilibrium processing of ferromagnetic heavily reduced
678 graphene oxide, *Carbon* 153 (2019) 663-673.

679 [36] M. B. Moghaddam, E.K. Goharshadi, M.H. Entezari, P. Nancarrow, Preparation,
680 characterization, and rheological properties of graphene–glycerol nanofluids, *Chem. Eng. J.*
681 231 (2013) 365-372.

682 [37] M. Hadadian, E.K. Goharshadi, A. Youssefi, Electrical conductivity, thermal
683 conductivity, and rheological properties of graphene oxide-based nanofluids, *J. Nanopart.*
684 *Res.* 16 (2014) 2788-2805.

685 [38] A. Pramanik, S. Maiti, M. Sreemany, S. Mahanty, Rock-Salt-Templated Mn_3O_4
686 Nanoparticles Encapsulated in a Mesoporous 2D Carbon Matrix: A High Rate 2 V Anode for
687 Lithium-Ion Batteries with Extraordinary Cycling Stability, *ChemistrySelect* 2 (2017) 7854-
688 7864.

689 [39] Q. Zhang, B. Wu, R. Song, H. Song, J. Zhang, X. Hu, Preparation, characterization and
690 tribological properties of polyalphaolefin with magnetic reduced graphene oxide/ Fe_3O_4 ,
691 *Tribol. Int.* 141 (2020) 105952-105962.

692 [40] C. W. Tang, C.-B. Wang, S.-H. Chien, Characterization of cobalt oxides studied by FT-
693 IR, Raman, TPR and TG-MS, *Thermochim. Acta* 473 (2008) 68-73.

694 [41] A. Dhakal, P. Wuytens, A. Raza, N. Le Thomas, R. Baets, Silicon nitride background in
695 nanophotonic waveguide enhanced Raman spectroscopy, *Materials* 10 (2017) 140-153.

696 [42] B. Sambandam, V. Soundharrajan, J. Song, S. Kim, J. Jo, P.T. Duong, S. Kim, V.
697 Mathew, J. Kim, Investigation of Li-ion storage properties of earth abundant β - $Mn_2V_2O_7$
698 prepared using facile green strategy, *J. Power Sources* 350 (2017) 80-86.

699 [43] G. Zhao, X. Huang, X. Wang, P. Connor, J. Li, S. Zhang, J.T. Irvine, Synthesis and
700 lithium-storage properties of MnO/reduced graphene oxide composites derived from graphene

701 oxide plus the transformation of Mn (VI) to Mn (II) by the reducing power of graphene oxide,
702 J. Mater. Chem. A 3 (2015) 297-303.

703 [44] H. Chen, M.Q. Wang, Y. Yu, H. Liu, S.-Y. Lu, S.-J. Bao, M. Xu, Assembling hollow
704 cobalt sulfide nanocages array on graphene-like manganese dioxide nanosheets for superior
705 electrochemical capacitors, ACS Appl. Mater. Interfaces 9 (2017) 35040-35047.

706 [45] Y. Li, Z. Yang, H. Zhang, X. Tong, J. Feng, Fabrication of sewage sludge-derived
707 magnetic nanocomposites as heterogeneous catalyst for persulfate activation of Orange G
708 degradation, Colloids Surf. A 529 (2017) 856-863.

709 [46] Y. Dai, M. Chen, X. Yan, J. Wang, Q. Wang, C. Zhou, D. Wang, H. Zhang, Y. Wang, X.
710 Cheng, Ultra-Small Fe₃O₄ Nanoparticles Decorated WS₂ Nanosheets with Superior
711 Electrochemical Properties for Supercapacitors, J. Nanosci. Nanotechnol. 19 (2019) 897-904.

712 [47] Z. Na, R. Yao, Q. Yan, X. Wang, X. Sun, X. Wang, A general strategy for enabling
713 Fe₃O₄ with enhanced lithium storage performance: Synergy between yolk-shell nanostructures
714 and doping-free carbon, Electrochim. Acta (2020) 137464-137471.

715 [48] A. Gangwar, A. Sharma, S. Shaw, S.S. Meena, N. Prasad, Structural and electrochemical
716 performance studies for nanocomposites of carbon with Fe₃C or Mn-Substituted (Fe₃C/Fe₃O₄)
717 as anodes for Li-batteries, Appl. Surf. Sci. 533 (2020) 147474-147484.

718 [49] C. Zhang, X. Cai, Y. Qian, H. Jiang, L. Zhou, B. Li, L. Lai, Z. Shen, W. Huang,
719 Electrochemically synthesis of nickel cobalt sulfide for high-performance flexible asymmetric
720 supercapacitors, Adv. Sci. 5 (2018) 1700375-1700387..

721 [50] M. Maggira, E.A. Deliyanni, V.F. Samanidou, Synthesis of graphene oxide based
722 sponges and their study as sorbents for sample preparation of cow milk prior to HPLC
723 determination of sulfonamides, Molecules 24 (2019) 2086-2101.

- 724 [51] A.K. Barick, D.K. Tripathy, Preparation, characterization and properties of acid
725 functionalized multi-walled carbon nanotube reinforced thermoplastic polyurethane
726 nanocomposites, *J. Mater. Sci. Eng. B* 176 (2011) 1435-1447.
- 727 [52] A. Jamsaz, E.K. Goharshadi, An environmentally friendly superhydrophobic modified
728 polyurethane sponge by seashell for the efficient oil/water separation, *Process Saf. Environ.*
729 *Prot.* 139 (2020) 297-304.
- 730 [53] N. Selvakumar, H.C. Barshilia, K. Rajam, Effect of substrate roughness on the apparent
731 surface free energy of sputter deposited superhydrophobic polytetrafluoroethylene coatings: A
732 comparison of experimental data with different theoretical models, *J. Appl. Phys.* 108 (2010)
733 013505-013515.
- 734 [54] A. Zdziennicka, J. Krawczyk, K. Szymczyk, B. Jańczuk, Components and parameters of
735 liquids and some polymers surface tension at different temperature, *Colloids Surf. A* 529
736 (2017) 864-875.
- 737 [55] E. Akdogan, M. Erdem, M.E. Ureyen, M. Kaya, Rigid polyurethane foams with halogen-
738 free flame retardants: Thermal insulation, mechanical, and flame retardant properties, *J. Appl.*
739 *Polym. Sci.* 137 (2020) 47611-47625.
- 740 [56] L. Dong, C. Hu, L. Song, X. Huang, N. Chen, L. Qu, A large-area, flexible, and flame-
741 retardant graphene paper, *Adv. Funct. Mater.* 26 (2016) 1470-1476.
- 742 [57] S. Wang, R. Gao, K. Zhou, The influence of cerium dioxide functionalized reduced
743 graphene oxide on reducing fire hazards of thermoplastic polyurethane nanocomposites, *J.*
744 *Colloid Interface Sci.* 536 (2019) 127-134.

745

746

747