



Characterization of nanodimensional Ni-Zn ferrite prepared by mechanochemical and thermal methods.

Elina Manova, Daniela Paneva, Boris Kunev, Éric Rivière, Claude Estournès, Ivan Mitov

► To cite this version:

Elina Manova, Daniela Paneva, Boris Kunev, Éric Rivière, Claude Estournès, et al.. Characterization of nanodimensional Ni-Zn ferrite prepared by mechanochemical and thermal methods.. Journal of Physics: Conference Series, 2010, 217 (1), pp.0. 10.1088/1742-6596/217/1/012102 . hal-03551039

HAL Id: hal-03551039

<https://hal.science/hal-03551039>

Submitted on 1 Feb 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

OPEN ACCESS

Characterization of nanodimensional Ni-Zn ferrite prepared by mechanochemical and thermal methods

To cite this article: E Manova *et al* 2010 *J. Phys.: Conf. Ser.* **217** 012102

View the [article online](#) for updates and enhancements.

You may also like

- [Electrochemical Determination of Sunitinib in Biological Samples Using Polyacrylonitrile Nanofibers/Nickel-Zinc-Ferrite Nanocomposite/Carbon Paste Electrode](#)
Ali Yarahmadi, Tayyeb Madrakian, Abbas Afkhami et al.
- [One-Pot Synthesis of Nanoporous Nickel Hydroxide Film as High-Performance Electrode for Asymmetric Supercapacitor](#)
Hongdan Wang, Liqiu Zhang, Lichun Liu et al.
- [Performance Enhancement of SOFC Anode Through Electrochemically Induced Ni/YSZ Nanostructures](#)
D. Klotz, B. Butz, A. Leonide et al.



The Electrochemical Society
Advancing solid state & electrochemical science & technology

242nd ECS Meeting

Oct 9 – 13, 2022 • Atlanta, GA, US

Abstract submission deadline: **April 8, 2022**

Connect. Engage. Champion. Empower. Accelerate.

MOVE SCIENCE FORWARD



Submit your abstract



Characterization of nanodimensional Ni-Zn ferrite prepared by mechanochemical and thermal methods

E Manova^{1,4}, D Paneva¹, B Kunev¹, E Rivière², C Estournès³ and I Mitov¹

¹ Institute of Catalysis, Bulgarian Academy of Sciences, Acad. G. Bonchev St., Block 11, 1113 Sofia, Bulgaria

² Institut de Chimie Moléculaire et des Matériaux d'Orsay, UMR 8182, UPS, 91405 Orsay, France

³ CNRS; Institut Carnot, Cirimat; F-31062 Toulouse, France

E-mail: elina@ic.bas.bg

Abstract. Nickel zinc ferrite nanoparticles, $\text{Ni}_{1-x}\text{Zn}_x\text{Fe}_2\text{O}_4$ ($x = 0, 0.2, 0.5, 0.8, 1.0$), with dimensions below 10 nm have been prepared by combining chemical precipitation with high-energy ball milling. For comparison, their analogues obtained by thermal synthesis have also been studied. Mössbauer spectroscopy, X-ray diffraction, and magnetic measurements are used for the characterization of the obtained materials. X-ray diffraction shows that after 3h of mechanical treatment ferrites containing zinc are formed, while 6h of treatment is needed to obtain NiFe_2O_4 . The magnetic properties of the samples exhibit a strong dependence on the phase composition, particle size and preparation method.

1. Introduction

The Ni-Zn ferrites have been extensively studied for various properties as well as for structural issues [1-4]. Zn and Ni are known to have very strong preferences for the tetrahedral and octahedral sites, respectively, making Ni-ferrite a model inverse ferrite and Zn-ferrite a model normal ferrite. The general formula of these materials is: $(\text{Zn}_x\text{Fe}_{1-x})_{\text{tetra}}[\text{Ni}_{1-x}\text{Fe}_{1+x}]_{\text{octa}}\text{O}_4$. Ni-Zn ferrite is of particular interest because the magnetic properties of the nanoparticles differ markedly from those of their bulk counterpart. It is of further interest to replace a non-magnetic Zn^{2+} ion by a magnetic Ni^{2+} in Zn-ferrite to understand the difference in the properties of the system of ferrites in the limit of nano-regime. The properties of these ferrites are highly sensitive to the cation distribution which in turn depends on the method of preparation and sintering conditions. Spinel-type ferrites can be prepared by a variety of methods [4-7]. The high-energy milling as a solid-state method for synthesis of nanodimensional materials has the advantage that it can be easily operated and produce large amounts of nanostructured powders in a fairly short time. Furthermore, the highly nonequilibrium nature of the milling process allows one to prepare solids with improved and/or novel physical and chemical properties.

The purpose of the present work was to investigate the possibility of synthesizing $\text{Ni}_{1-x}\text{Zn}_x\text{Fe}_2\text{O}_4$ ($x = 0, 0.2, 0.5, 0.8, 1.0$) nanodimensional powders by co-precipitation of the corresponding hydroxide

⁴ To whom any correspondence should be addressed.

carbonates followed by mechanochemical or thermal treatment. The relationship between synthesis method, phase composition and structural properties of the obtained materials was investigated.

2. Experimental

The mechanochemical synthesis (MS) of nickel-zinc ferrite powders was performed by two steps: (i) co-precipitation, and (ii) high-energy ball-milling (3h to obtain $\text{Ni}_{1-x}\text{Zn}_x\text{Fe}_2\text{O}_4$ ($x = 0.2, 0.5, 0.8, 1.0$) and 6h for NiFe_2O_4) following the procedure, described in [7]. The thermal synthesis (TS) was performed by annealing of the co-precipitation precursors at 773 K.

The phase composition and structure was determined by X-ray diffraction (XRD) using TUR M62 diffractometer with Co $K\alpha$ radiation. Data interpretation was carried out using JCPDS (Joint Committee on Powder Diffraction Standards) database. Transmission ^{57}Fe Mössbauer spectra were obtained at room temperature (RT) with a Wissel electromechanical Mössbauer spectrometer (Wissenschaftliche Elektronik GmbH, Germany) working at a constant acceleration mode. A $^{57}\text{Co}/\text{Cr}$ (activity $\cong 20$ mCi) source and an $\alpha\text{-Fe}$ foil standard were used. Experimentally obtained spectra were treated using the least squares method. The parameters of hyperfine interactions such as isomer shift (δ), quadrupole splitting (Δ) and effective internal magnetic field (B) as well as the line widths (Γ) and the relative weight (G) of the partial components of the spectra were determined. Isothermal magnetizations of the Ni-Zn ferrites were measured on a Quantum Design SQUID Magnetometer.

3. Results and discussion

The XRD patterns of the co-precipitated precursors (not shown) are characteristic of layered double hydroxides as found for Pyroaurite (PDF 25-0521) and Hydrotalcite (PDF 41-1428). After 3h of milling the diffraction lines of the spinel phases $\text{Ni}_{1-x}\text{Zn}_x\text{Fe}_2\text{O}_4$ ($x = 0.2, 0.5, 0.8, 1.0$) are well defined, while NiFe_2O_4 is obtained after 6h of mechanical treatment. The diffractograms of all mechanochemically synthesized samples are composed of broadened low intensity peaks, suggesting very small particles dimensions. For all thermally treated samples $\text{Ni}_{1-x}\text{Zn}_x\text{Fe}_2\text{O}_4$ ferrites are obtained. The average crystallites size (D), the degree of microstrain (ϵ), and the lattice parameter (a) of the studied nickel-zinc ferrites are also determined from the experimental XRD profiles (Table 1) by using the Williamson-Hall analysis. A well defined effect of the crystals size decrease and increase in the crystal defects and lattice parameter is observed for the mechanochemically obtained materials (Table 1). A dependence of the lattice parameter on the preparation method and the phase composition exists.

Table 1. Crystallite size (D), microstrain (ϵ) and lattice parameter (a) of investigated sample.

Sample	D (nm)	$\epsilon \cdot 10^3$ (a.u.)	a (Å)
NiFe_2O_4 , TS	19.30	1.599	8.332
$\text{Ni}_{0.8}\text{Zn}_{0.2}\text{Fe}_2\text{O}_4$, TS	19.34	1.233	8.363
$\text{Ni}_{0.5}\text{Zn}_{0.5}\text{Fe}_2\text{O}_4$, TS	24.60	0.646	8.387
$\text{Ni}_{0.2}\text{Zn}_{0.8}\text{Fe}_2\text{O}_4$, TS	26.00	0.427	8.416
ZnFe_2O_4 , TS	28.67	2.275	8.432
NiFe_2O_4 , MS	5.32	15.945	8.381
$\text{Ni}_{0.8}\text{Zn}_{0.2}\text{Fe}_2\text{O}_4$, MS	5.32	15.974	8.396
$\text{Ni}_{0.5}\text{Zn}_{0.5}\text{Fe}_2\text{O}_4$, MS	5.83	14.268	8.403
$\text{Ni}_{0.2}\text{Zn}_{0.8}\text{Fe}_2\text{O}_4$, MS	11.24	3.700	8.422
ZnFe_2O_4 , MS	10.16	5.398	8.444

The Mössbauer spectra of the precursors exhibits a quadrupole doublet with $\delta=0.34$ mm/s and $\Delta=0.65\text{--}0.70$ mm/s, indicating that the hydroxide carbonates are paramagnetic. Figure 1 shows the RT Mössbauer spectra of samples obtained after different processing routes. The corresponding parameters, listed in Table 2, are typical of Fe^{3+} ions in octahedral and tetrahedral spinel sites [1, 6, 7].

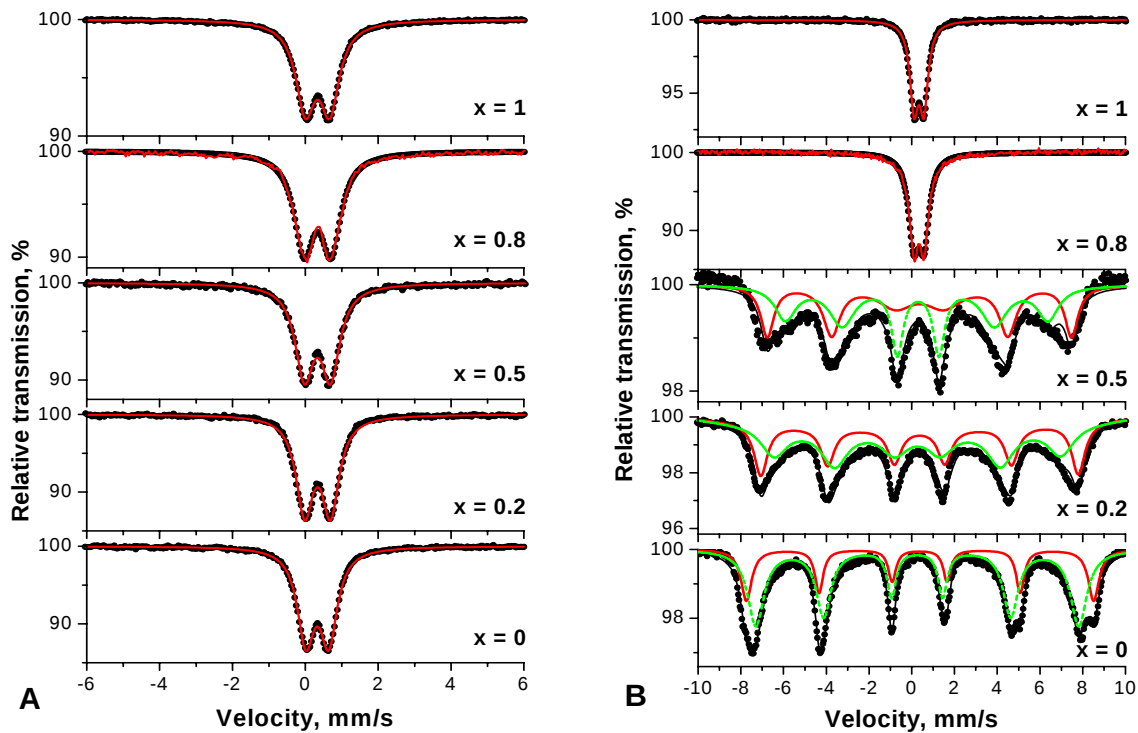


Figure 1. RT Mössbauer spectra of mechanochemically (A) and thermally (B) synthesized $\text{Ni}_{1-x}\text{Zn}_x\text{Fe}_2\text{O}_4$. (— Fe^{3+} octa; - - - Fe^{3+} tetra)

Table 2. Parameters of Mössbauer spectra.

Sample	Components ^a		δ (mm/s)		Δ (mm/s)		B (T)		Γ (mm/s)		G (%)	
	MS	TS	MS	TS	MS	TS	MS	TS	MS	TS	MS	TS
ZnFe_2O_4	Db	Db	0.34	0.34	0.70	0.46	-	-	0.64	0.48	100	100
$\text{Ni}_{0.2}\text{Zn}_{0.8}\text{Fe}_2\text{O}_4$	Db	Db	0.34	0.34	0.77	0.49	-	-	0.66	0.59	100	100
$\text{Ni}_{0.5}\text{Zn}_{0.5}\text{Fe}_2\text{O}_4$	Db	Sx1	0.33	0.37	0.72	0.00	-	44.3	0.62	1.00	100	47
		Sx2		0.27		0.00		38.2		1.50		53
$\text{Ni}_{0.8}\text{Zn}_{0.2}\text{Fe}_2\text{O}_4$	Db	Sx1	0.33	0.37	0.71	0.00	-	46.2	0.57	0.75	100	42
		Sx2		0.27		0.00		41.7		1.50		58
NiFe_2O_4	Db	Sx1	0.33	0.37	0.63	0.00	-	50.6	0.57	0.54	100	37
		Sx2		0.27		0.00		46.9		0.78		63

^a Db = doublet (Fe^{3+} octa); Sx1 = sextet (Fe^{3+} octa); Sx2 = sextet (Fe^{3+} tetra)

As shown in Figure 1A the spectra of all milled samples are doublets. It is well known that the magnetic characteristics of the material are strongly affected when the particle size becomes very small, due to the influence of thermal energy on the magnetic moment ordering, originating the superparamagnetic (SPM) relaxation phenomenon. Taking into account the XRD data we suppose that the doublets observed in all milled samples arise from Fe^{3+} ions in ultrafine ferrite particles exhibiting SPM behavior. This particle size effect is confirmed by the RT isothermal magnetizations where the absence of saturation in the magnetic field range explored, the “S” shape of the curves together with the lack of coercivity indicate the presence of SPM particles.

A difference in structure between the materials, depending on the preparation method is observed. The spectra of ZnFe_2O_4 and $\text{Ni}_{0.2}\text{Zn}_{0.8}\text{Fe}_2\text{O}_4$ formed by co-precipitation and thermal treatment show

only doublet components (Figure 1B). Comparing with mechanochemically synthesized ZnFe_2O_4 and $\text{Ni}_{0.2}\text{Zn}_{0.8}\text{Fe}_2\text{O}_4$ we note that the average isomer shifts show no significant variation thus indicating that the s-electron charge distribution of Fe^{3+} ions is negligibly influenced by the synthesis method. But the quadrupole splitting and the spectral line width of the Zn rich ferrite particles are larger for the MS samples (Table 2). This broadening is likely to be associated with several effects induced by milling. As the average grain size decreases, the fraction of disordered and interfacial regions increases and changes in the site distributions of Fe^{3+} and Zn^{2+} ions as well as changes in tetrahedral and octahedral bond lengths and angles probably occur. The isothermal magnetization at RT confirms the paramagnetic character of the TS zinc ferrite, while the mechanochemically obtained sample is superparamagnetic. A magnetic ordering of ZnFe_2O_4 is possible only if there is an inversion of cation distribution – some of the Zn^{2+} ions occupy the octahedral sites and some of the Fe^{3+} ions occupy the tetrahedral sites. Therefore the milling process induces structural transformation of the spinel with cationic redistribution into the system which induces magnetic ordering of the ferric ions leading to changes in the magnetic behavior of the materials.

On the other hand, the Mössbauer spectra of thermally synthesized NiFe_2O_4 , $\text{Ni}_{0.8}\text{Zn}_{0.2}\text{Fe}_2\text{O}_4$ and $\text{Ni}_{0.5}\text{Zn}_{0.5}\text{Fe}_2\text{O}_4$ exhibit magnetic splitting at RT. The registered broad spectral lines are probably due to SPM relaxation and Fe^{3+} disorder with increase of Zn-content. As zinc is introduced in the system, the effective internal magnetic field B is reduced. The variation of B with zinc introduction can be explained on the basis of Yafet-Kittel type of spin arrangement [8]. With the increase in zinc concentration, the Fe^{3+} ions will have no magnetic neighbors and hence spins become uncoupled, the saturation magnetization decreases, and hence the hyperfine field decreases. Smaller values of the RT isothermal magnetizations are registered for the MS phases and could be related to local canting of magnetic ions due to the imperfect structure, and mainly to the surface effect of nanosize particles of large surface area.

4. Conclusions

In this work it has been demonstrated that the high-energy ball milling of layered nickel-zinc-iron hydroxide carbonates results in the formation of nanocrystalline Ni-Zn ferrites, where the particle size is below 10 nm. The zinc introduction facilitates the ferrite formation. The structural and magnetic properties of the samples exhibit a strong dependence on the phase composition, particle size and preparation method. This work shows that the combination of the co-precipitation method and subsequent mechanical milling is a promising technique for a relatively large scale preparation of Ni-Zn ferrite nanoparticles.

Acknowledgements

The authors thank the National Science Fund of Bulgaria for financial support through Projects X-1504/05 and Rila4-412 (DO 02-295/2008).

References

- [1] Upadhyay C, Verma H C and Anand S, 2004 *J. Appl. Phys.* **95** 5746–51
- [2] Elizalde Galindo J T, Adair A H, Botez C E, Corral Flores V, Bueno Baques D, Fuentes Cobas L and Matutes-Aquino J A 2007 *Appl. Phys. A* **87** 743–74
- [3] Bercoff P G and Bertorello H R 2000 *J. Magn. Magn. Mater.* **213** 56–62
- [4] Albuquerque A S, Ardisson J D, Macedo W A A and Alves M C M 2000 *J. Appl. Phys.* **87** 4352–57
- [5] Cabanas A and Poliakoff M 2001 *J. Mater. Chem.* **11** 1408–16
- [6] Roy M K and Verma H C 2006 *J. Phys.: Condens. Matter* **18** 7273–7281
- [7] Manova E, Kunev B, Paneva D, Mitov I, Petrov L, Estournès C, d'Orléans C, Rehspringer J L and Kurmoo M 2004 *Chem. Mater.* **16** 5689–96
- [8] Murthy N S S, Natera M G, Youssef S I, Begum R J and Srivastava C M 1969 *Phys. Rev. B* **181** 969–77