



**HAL**  
open science

## Towards a white LED based on rare earth-doped ZnO

J Frieiro, C Guillaume, J López-Vidrier, O Blázquez, S González-Torres, C Labbé, S Hernández, Xavier Portier, B Garrido

► **To cite this version:**

J Frieiro, C Guillaume, J López-Vidrier, O Blázquez, S González-Torres, et al.. Towards a white LED based on rare earth-doped ZnO. *Nanotechnology*, 2020, 31 (46), pp.465207. 10.1088/1361-6528/abadc9 . hal-03612706

**HAL Id: hal-03612706**

**<https://hal.science/hal-03612706v1>**

Submitted on 18 Mar 2022

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Towards a white LED based on rare earth-doped ZnO

J.L. Frieiro,<sup>1,2</sup> C. Guillaume,<sup>3</sup> J. López-Vidrier,<sup>1,2</sup> O. Blázquez<sup>1,2</sup>, S. González-Torres<sup>1,2</sup>  
C. Labbé,<sup>3</sup> S. Hernández,<sup>1,2</sup> X. Portier,<sup>3</sup> B. Garrido<sup>1,2</sup>

<sup>1</sup>MIND, Departament d'Enginyeria Electrònica i Biomèdica, Universitat de Barcelona, Martí i Franquès 1, 08028 Barcelona (Spain)

<sup>2</sup>Institute of Nanoscience and Nanotechnology (IN<sup>2</sup>UB), Universitat de Barcelona, Av. Joan XXIII S/N, 08028 Barcelona (Spain)

<sup>3</sup>Normandie Université, ENSICAEN, UNICAEN, CEA, UMR CNRS 6252, CIMAP, 6 Boulevard du Maréchal Juin, 14050 Caen (France)

**Keywords:** light emitting devices, electroluminescence, rare earths, RGB, ZnO

## Abstract

By using ZnO thin films doped with Ce, Tb or Eu, we have developed monochromatic (blue, green and red, respectively) light emitting devices. The rare earth ions introduced exhibit narrow and intense emission peaks due to electronic transitions in relaxation processes induced after electrical excitation. This study proves zinc oxide to be a good host for these elements, its high conductivity and optical transparency in the visible range being as well exploited as top transparent electrode. After structural characterization of the different doped layers, a device structure with intense electroluminescence is presented, modelled and electrically and optically characterized. The different emission spectra obtained are compared in a chromatic diagram, providing a reference for future works with similar devices.

## Introduction


For decades now, zinc oxide (ZnO) has attracted the attention of a large part of the optoelectronics research community. This well-known transition metal oxide exhibits a wurzite structure, a direct bandgap with an energy of 3.4 eV and a large exciton binding energy (60 meV),<sup>[1]</sup> making this material suitable for many applications including thin film transistors, light emitters, detectors and gas sensors.<sup>[2,3]</sup> Its high transparency to visible light (> 80%) and good conductivity ( $\sim 100 \Omega^{-1} \text{ cm}^{-1}$ ) have also made it a promising transparent conductive oxide (TCO), boosted in many cases by the doping of elements like Al, which further increases the conductivity while maintaining a high transparency.<sup>[4,5]</sup> In the context of light emission, it has been compared to gallium nitride (GaN), as they both arrange in the same crystalline structure and present very similar bandgap energy although they significantly differ in exciton binding energy, 25 meV for GaN, which in principle makes ZnO more suitable for light emission. The advantage of GaN over ZnO comes in the easier fabrication of *p*-type films, the tunability of the bandgap (and thus light emission energy) from the UV to the near IR when alloyed with In and/or Al (AlInGaN alloys) and the lower sensibility to defects and dislocations as non-radiative recombination centers.<sup>[6]</sup> Nevertheless, both the abundance of Zn compared to Ga and higher exciton stability of ZnO at room temperature, together with its non-toxicity, still make ZnO relevant for optoelectronic applications.

In the case of ZnO, it is a semiconductor that intrinsically presents oxygen vacancies ( $V_o$ ) and zinc interstitials ( $Zn_i$ ) that act as donor impurities,<sup>[7]</sup> being possible to control them during the fabrication or posterior annealing processes. This particularity is of special interest for producing good *n*-type ZnO layers, further enhanced by doping with group-III elements such as Al, Ga and In as substitutes for Zn sites or group-VII elements such as Cl and I as substitutes for O ones. Nevertheless, reliable *p*-type layers remain a major challenge because of the self-compensation from those native donor defects. Some efforts have been done in this direction using group-I (substitutes for Zn) or group-V (for O) elements, or by alloying it with Mg.<sup>[8,9]</sup> Therefore, the achievement of electroluminescence devices based on a ZnO p-n junction still has to overcome this issue.

Due to this last limitation, a different strategy employed for producing ZnO-based light emitting devices (LEDs) is based on the doping with already optically-active centers. In this context, rare earth (RE) elements have demonstrated over decades outstanding optical and electroluminescent (EL) properties.<sup>[10]</sup> Among all these, it is especially notable the intense, stable and narrow emission they present, the different RE species covering a wide range of the electromagnetic spectrum, in some cases spanning from the near-infrared (NIR) to ultraviolet (UV).<sup>[11]</sup> Their hosting material specially affects the scattering of the emission, which is larger for polycrystalline and amorphous materials and weaker for crystalline matrices. RE elements are being employed by the industry for the fabrication of LEDs as part of phosphorescent stacks in an optical down conversion process. Additionally, the suitability of different host matrices,<sup>[10,12,13]</sup> including ZnO,<sup>[14–17]</sup> for hosting optically-active RE dopants has been extensively proven in the past, aiming at profiting from their emission after electrical excitation.

The emission process in RE is due to the electronic transitions within the inner *f*-shell of these elements (from the 4<sup>th</sup> or 5<sup>th</sup> levels for lanthanides and actinides, respectively), leading to photon emission with an energy dependent on those transitions. Initially, RE elements have their outer *f*-shell partially filled. In a  $C_{4v}$  they have a +3-valence state as a result of the loss of the two electrons from the outer *s*-shell and one from the partially filled *f*-shell. This valence state is possible in ZnO-doped films when the RE ions occupy Zn sites. In this configuration, excited lanthanide ions can relax through the predominant intra-*4f* (practically independent on the local environment) and *5d*-to-*4f* (quite sensible to the matrix and local environment) electronic transitions,<sup>[18–20]</sup> leading to intense narrow emission peaks.

Regarding research in the field of LEDs, of particular interest would result the finding of a red-green-blue (RGB) system able to be employed as full-color light source. Bearing this objective in mind, in this work we have studied three of these RE elements: europium (Eu), terbium (Tb) and cerium (Ce). In **Figure 1**, the main electronic transitions involved in the emission of these three elements are represented.<sup>[14,21,22]</sup> Please note that the more probable transitions, thus resulting in more intense emissions, are indicated in color referring to their apparent color: red for Eu (616 nm), green for Tb (544 nm) and blue for Ce (464 nm).

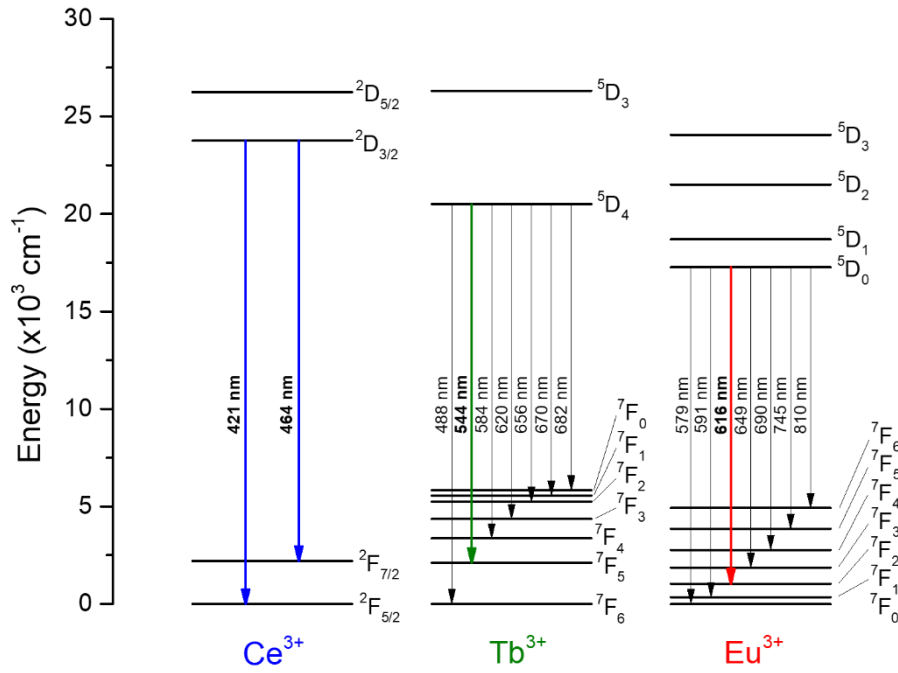

**Figure 1.** 5d-to-4f electronic transitions in the rare earth ions considered for this work ( $\text{Ce}^{3+}$ ,  $\text{Tb}^{3+}$  and  $\text{Eu}^{3+}$ ) and the wavelength corresponding to the resulting photons. The main transitions have been highlighted in the schematics in blue, green and red, respectively for  $\text{Ce}^{3+}$ ,  $\text{Tb}^{3+}$  and  $\text{Eu}^{3+}$ .

Due to the precise conditions required for the optical activation of RE ions, the doping,<sup>[15]</sup> fabrication process<sup>[23]</sup> or local environment<sup>[16,24–26]</sup> become critical factors to obtain reliable devices that take profit of their luminescent properties. In this work, we have fabricated Re-doped ZnO layers by radiofrequency (RF) magnetron sputtering onto *n*-type Si substrates, with an atomic-layer-deposited (ALD) ZnO as top transparent electrode. Three different RE-species have been employed, Eu, Tb and Ce, for emitting, as discussed above, in the red, green and blue, respectively. The structural properties have been characterized by transmission electron microscopy (TEM) and electron diffraction of X-rays (EDX), allowing determining the spatial distribution of the RE-ions at the nanoscale. Electrical characterization has revealed different conduction mechanisms that can be related to the structural properties of the layers and the device configuration. Finally, all the studied devices exhibit EL as a consequence of the excitation of the RE-species. The obtained emissions are discussed in terms of the different RE species, the structural and electrical properties. The results here presented get us closer to achieving an RGB-color or white LED fabricated with a base on abundant materials such as Si and Zn, taking advantage of the emission from RE ions as optical centers.

## Materials and methods

The ZnO films were deposited from ZnO targets on a *n*-type (100)-oriented Si substrate via a 3-inch RF magnetron sputtering system, using a power density of  $0.96 \text{ W}\cdot\text{cm}^{-2}$ , 15  $\mu\text{bar}$  of pressure, Ar flux of 2 sccm, and at a substrate temperature of 400 °C. During deposition, the targets of RE oxide (either  $\text{CeO}_2$ ,  $\text{Tb}_4\text{O}_7$ , or  $\text{Eu}_2\text{O}_3$ ) were placed in a circular distribution for homogeneously doping the ZnO films. To avoid cross-contamination, three different ZnO targets nominally identical were used for each of the three different dopant species. Under these conditions, three 60-nm-thick single-layer samples have been deposited: (i) ZnO:Eu,Tb, (ii)

ZnO:Tb, and (iii) ZnO:Ce. An additional sample containing the three RE species was fabricated by consecutively depositing 20-nm-thick layers of the three mentioned films in a (iv) ZnO:Ce/ZnO:Tb/ZnO:Eu,Tb structure. The nominal RE doping concentration is ~1 at.% in ZnO:Ce, ~2 at.% in ZnO:Tb, and 0.8 at.% of Eu and ~1.6 at.% of Tb in ZnO:Eu,Tb, being these values in accordance with the atomic concentration of REs of the targets. Afterwards, all samples underwent an annealing process for 1 hour at 700 °C in a N<sub>2</sub> atmosphere. The top 100-nm-thick ZnO electrode was deposited by means of atomic layer deposition (ALD) at a deposition temperature of 200 °C, resulting in a highly-conductive layer (conductivity > 100 Ω<sup>-1</sup> cm<sup>-1</sup>) with an optical transparency of ~85% through the visible range.<sup>[4]</sup> Afterwards, circular contacts with 500 μm diameter were patterned via conventional photolithography. Finally, a full-area deposition by electron beam evaporation (EBE) of Al created the common bottom electrode to finalize the devices.

Structural characterization by electron microscopy was done in a duplicate of sample (iv), as it can provide representative information of the deposition for the three films under investigation. The foils were prepared by focused ion beam (FEI Helios Nanolab 660), and their structure was analyzed at the nanoscale by conventional and high resolution TEM (HRTEM) using a double-corrected cold FEG ARM200F JEOL microscope, operated at 200 kV and equipped with a high-angle annular dark field (HAADF) detector and an EDX Centurio spectrometer. EDX profiles were acquired along a 75-nm straight line across the film with 120 probed spots and 1 second acquisition time per spot.

Current-voltage [*I*(*V*)] measurements were carried out placing the devices within a Cascade Microtech Summit 11000 probe station coupled to an Agilent B1500A semiconductor device analyzer. A Faraday cage is used to isolate the devices from external electromagnetic noise. In all electrical measurements, a voltage was applied on the top ZnO contact while the bottom Al was grounded through the chuck of the system. The voltage applied this way was swept in steps of 50 mV·s<sup>-1</sup>. EL emission from the devices was collected by a microscope with a 20× NIR objective with a numerical aperture of 0.4, and it was spectrally resolved via a 1/4m monochromator and a LN-cooled charge coupled device (CCD) in the 350 nm to 1100 nm range. Integrated EL was also collected by replacing the monochromator-CCD system by a GaAs photomultiplier tube (PMT), sensitive in the range from 350 nm to 900 nm.

## Results


### a. Structural characterization

Figure 2 shows a HRTEM image (Figure 2a) of sample (iv) and the EDX analysis performed (Figure 2b) for the elements present in the sample along growth direction, as indicated by the line in the HRTEM image. In Figure 2a, different regions on the sample can be clearly identified. From the bottom, it can first be found the *n*-type Si substrate with a ~5-nm layer of native SiO<sub>x</sub> on top, which was intentionally left unremoved before the deposition process. The deposited RE-doped ZnO films can be observed above the SiO<sub>x</sub>. Please note here that there is no indication of the existence of any interface between each ZnO layer, despite the different steps for depositing all ZnO layers. On top of the stack, Pt was deposited in order to cut the sample by FIB. The doped-ZnO total thickness was measured to be ~65 nm and its polycrystalline nature can be clearly distinguished in the image by the different crystalline plane orientations present in the film.

To assess the composition of the layers, EDX measurements were done along the vertical line indicated in Figure 2a. The atomic profiles corresponding to Pt (black), Si (grey), Ce (blue), Tb (green) and Eu (red) are plotted in Figure 2b. As shown in the TEM image, Si is only present at

the bottom of the sample, whereas Pt is only present on top. To compare the concentration of each RE element and each film, vertical lines have been drawn approximately where the profiles of the elements change, therefore suggesting the interface between the different sublayers. The intended nominal thickness for each sublayer was 20 nm. However, the actual thickness (indicated in the graph) slightly differ; in particular, it can be observed that the Ce-doped layer is ~8 nm thinner than the Tb-doped and Tb- and Eu-codoped ones.

The EDX results also reveals the non-homogeneity of the RE ions within the layers: whereas Tb is uniformly distributed along the ZnO:Tb layer, the other two layers present a high agglomeration of the RE ions in certain zones: on one hand, Ce is accumulated at the top of the third layer, in a small region of ~5 nm; on the other hand, in the first layer Tb continues to be well distributed until the interface with Si is reached, where both Tb and Eu also have accumulated in a region of ~8 nm.

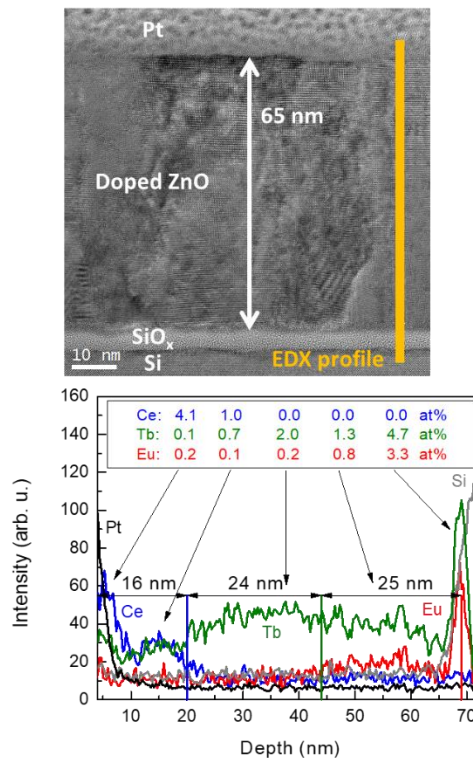


**Figure 2.** (a) TEM image corresponding to the deposited sample containing the ZnO:Ce/ZnO:Tb/ZnO:Eu,Tb stack, being the total stack thickness measured to be ~65 nm. (b) EDX depth profiles for Pt, Si, Ce, Tb and Eu, obtained through 120 points measured along the 75 nm indicated with a vertical a line in (a).

### b. Electrical characterization

Initially, an electrical characterization via  $I(V)$  measurements was performed in order to understand the conduction regime governing each single-layer device. **Figure 3** displays the  $I(V)$  curves for the ZnO:Ce (blue), ZnO:Tb (green), ZnO:Eu,Tb (red) and ZnO:Ce/ZnO:Tb/ZnO:Eu,Tb (orange) devices in a range from -8 V to 10 V. A sketch of the devices structure and their electrical connections during measurements is displayed in the inset at the bottom right corner. A first glance to **Figure 3a** reveals a large rectification behavior in all three samples, exhibiting well-differentiated current level under forward and reverse biasing (V

$> 0$  and  $V < 0$ , respectively). This rectification is a consequence of the heterojunction formed by the different layers composing the device structure, and it is directly correlated with its energy band diagram. For forward bias, both ZnO:Tb and ZnO:Eu,Tb devices show a similar conduction behavior, resembled at one order of magnitude lower by ZnO:Ce/ZnO:Tb/ZnO:Eu,Tb and different from the line-shape exhibited by ZnO:Ce. Despite this, all four device structures present a pronounced change in the  $I(V)$  curve around 7 V, that could be associated with a change in the carrier transport through the structure as will be further covered.

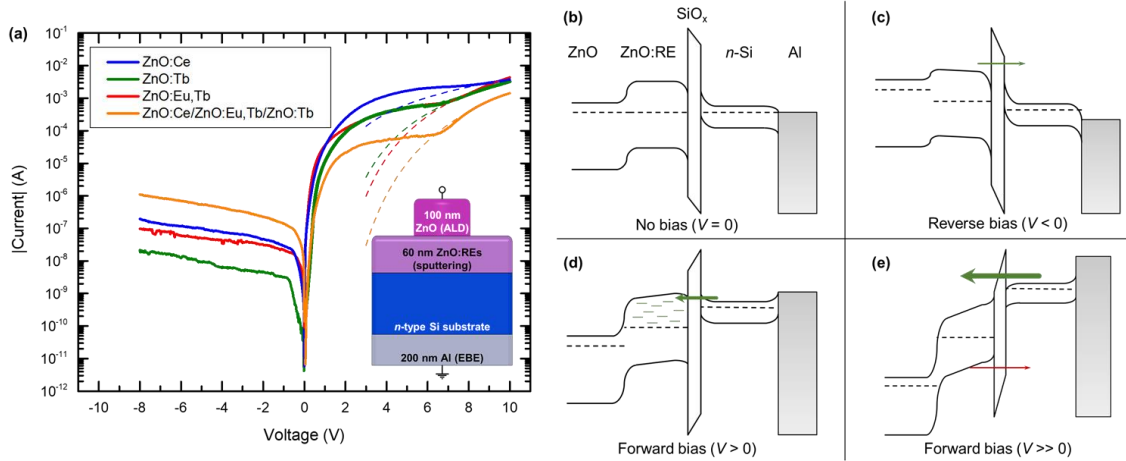

**Figure 3.** (a)  $I(V)$  curves corresponding to the devices with ZnO:Ce, ZnO:Tb and ZnO:Eu,Tb active layers in the range from  $-8$  V to 10 V, respectively represented with a blue, green, red and orange line. Dashed lines present a Fowler-Nordheim fitting for each curve at high voltages. Inset sketch shows the structure of the devices under study. (b) Schematic energy band diagram for the device structure, with each layer labelled, under no applied bias. (c) Modified energy band diagrams under the application of reverse bias. (d), (e) Band diagrams under low and high forward biasing, respectively. Green and red arrows indicate the direction of the injected electrons and holes, respectively.

The observed trends can be explained in terms of the energy band diagrams of our devices. Bearing in mind our device configuration and the electronic band structure of the different layers, we have depicted in **Figures 3b, c, d and e**, the energy band diagrams for the device structure under four different bias conditions: (b) no bias, (c) reverse and (d), (e) forward bias. The top ZnO electrode and the  $n$ -type substrate present high electronic densities, with the energy Fermi level close to the bottom of the conduction band, whereas the RE-doped ZnO has been considered an intrinsic (or quasi-intrinsic) semiconductor, with the energy Fermi level practically in the middle of the band gap. Under no bias conditions (see **Figure 3b**), the energy Fermi levels are aligned along the whole structure, having carriers blocked by two energy barriers at both sides of the  $\text{SiO}_x$  dielectric layer: a depletion region at the  $\text{SiO}_x$ -Si interface and an accumulation of electrons at the ZnO- $\text{SiO}_x$  interface. When the devices are set under reverse bias ( $V < 0$ ), the current rapidly increases up to 1 V, where the extracted current saturates (see **Figure 3a**). Below 1 V, the applied voltage is weak for promoting efficient tunneling but it contributes to the extraction of carriers from traps and defects, leading to a high current increase. Further increasing the applied voltage, as it can be seen in **Figure 3c**, maintains the dielectric barrier of  $\text{SiO}_x$  while increasing the depletion region in the Si substrate. This is partially compensated by an increase of the accumulation region in the ZnO layer. The overall result is that the barrier scales with the applied external voltage, allowing some electrons to tunnel through the barrier. As the applied bias increases in absolute value, the number of

electrons with enough energy to tunnel also increases, thus resulting in the slight enhancement in the measured current in agreement with our experimental observations.

On the other hand, the devices present a rapid growth under forward bias ( $V > 0$ ). In this polarity, as it can be seen in [Figure 3d](#), the accumulation region at the ZnO-SiO<sub>x</sub> interface is reduced until it soon shifts to a depletion region. As well, the depletion region initially present at the SiO<sub>x</sub>-Si interface is rapidly reduced with the applied voltage. The combination of these two effects taking place allows for a faster rate of electrons to tunnel through the SiO<sub>x</sub> barrier from the Si substrate to the RE-doped ZnO. It should be noted here that the doped-ZnO layer is polycrystalline and considered quasi-intrinsic, thus it may contain a large number of inter-band gap traps due to defects. At very low voltages ( $V < 1.6$  V) charge transport is again associated to carrier extraction from traps and defects (as previously identified for reverse bias conditions). As voltage increases and tunneling through the dielectric is enabled ( $1.6$  V  $< V < 7$  V), a similar behavior to ohmic transport is observed due to a hopping mechanism of the electrons through the traps in the doped ZnO band gap, being the current bulk-limited. With the increase in applied external voltage the traps are rapidly filled and current increases until reaching a trap-filled limit, after which the current becomes limited due to space charge.

From the  $I(V)$  curves, it is evident that there is change in conduction above 7 V for all devices. High applied external voltages can induce an accumulation region at the SiO<sub>x</sub>-Si interface, once the depletion region is completely compensated (see [Figure 3e](#)), whilst the depletion region at the ZnO-SiO<sub>x</sub> interface increases. Under these conditions, the energy bands of SiO<sub>x</sub> dielectric layer is also bent and electrons are thus able to tunnel through a reduced triangular barrier following a Fowler-Nordheim (FN) mechanism. Assuming that FN is the main conduction mechanism in this regime, the  $I(V)$  curves at high voltages should follow:

$$I = a V^2 e^{(b/V)},$$

where  $a$  and  $b$  are constants. Indeed, we have fitted all  $I(V)$  curves by this mechanism (see dashed lines in [Figure 3a](#)), showing an excellent agreement with the experimental data.

In order to estimate the minimum voltage for FN conduction, we have taken into account the energy band diagram of the device structure in this range of voltages (see [Figure 3e](#)) and evaluated its series resistance. To this end, some considerations have been made, treating the SiO<sub>x</sub> barrier as SiO<sub>2</sub>: (i) Flat band voltage can be calculated supposing that the Fermi level of  $n$ -Si is close to the conduction band and the ZnO-Fermi level in the middle of its band gap (at 1.70 eV from the bottom of the conduction band). Adding the electron affinity difference between ZnO and Si (4.50 and 4.05 eV, respectively), it results in a flat band voltage of 2.15 V. (ii) The minimum voltage required for overcoming the offset energy between Si and SiO<sub>2</sub> tunneling from the Si conduction band is equal to the difference in their electron affinities (4.05 eV for Si and 0.90 eV for SiO<sub>2</sub>), that is, 3.15 eV. (iii) Finally, the series resistance (and thus the voltage drop) can be numerically evaluated for each  $I(V)$  curve within the FN regime, using an iterative method. The resulting values from this procedure are summarized in [Table I](#). Adding these three terms we can estimate the minimum voltages for each device as it appears in the last column of [Table I](#). The FN fittings shown in [Figure 3a](#) employ this minimum voltage as lower limit for the fitting range.



**Table I.** Calculation of the minimum required external voltage to enter the FN tunneling regime.

| Device                  | Flat-band voltage (V) | SiO <sub>2</sub> bending voltage (V) | Series resistance (R <sub>s</sub> , in FN) (kΩ) | Voltage drop (due to R <sub>s</sub> ) (V) | Minimum voltage for FN (V) |
|-------------------------|-----------------------|--------------------------------------|---|---|----------------------------|
| ZnO:Ce                  | 2.15                  | 3.15                                 | 1.21  | 3.32                                      | 8.62                       |
| ZnO:Tb                  |                       |                                      | 1.79  | 1.13                                      | 6.43                       |
| ZnO:Eu,Tb               |                       |                                      | 1.51  | 0.7                                       | 6.00                       |
| ZnO:Ce/ZnO:Eu,Tb/ZnO:Tb |                       |                                      | 10.9  | 0.79                                      | 6.09                       |

As previously commented, the conduction under forward bias slightly differs for ZnO:Ce when compared to the other two films. This is probably due to the larger concentration of Ce with respect to the other two RE elements in their respective films, added to an easier oxidation process.<sup>[27,28]</sup> These two facts could result in a combination of large clustering of Ce<sup>3+</sup> and oxidation to Ce<sup>4+</sup>, generating additional defect-related traps within the ZnO layer that require a larger external applied voltage to be filled. In addition, the clustering of Ce is in line with the EDX measurements, which showed an 8-nm thinner Ce film in the tri-layer system compared to the other two. Nevertheless, once the traps are filled FN dominates the conduction, in this case, for  $V > 8.62$  V. For devices with the ZnO:Ce/ZnO:Tb/ZnO:Eu,Tb stack, the deposition of multiple layers generates additional grain boundaries which can be directly related to the increase in the series resistance. While conduction is still dominated by FN at high voltages due to the presence of traps in the doped-ZnO layer, the high series resistance hinders their conductivity by one order of magnitude.


### c. Electroluminescence emission


The complete analysis on the EL properties of the RE-doped ZnO devices is detailed in **Figure 4**. In all devices, emission has only been observed under forward bias, in agreement with the higher charge injection under this condition, as determined by  $I(V)$  measurements. Prior to spectrally resolving the EL of the devices, its integrated collection helped identifying the emission threshold and the relation of the emission with current, and thus the applied external voltage. For these measurements, the applied voltage was swept from 0 to 8 V in steps of 0.1 V·s<sup>-1</sup>. The results of this study are displayed in **Figure 4a**, following the color scheme of the devices analyzed in **Figure 3a**. Both ZnO:Tb and ZnO:Eu,Tb present again similar behaviors, with emission thresholds at 200-500 μA. This threshold is increased to 1 mA in ZnO:Ce, thus indicating a less efficient emission. In the case of the multilayer device, the threshold is reduced to 10 μA, signaling a higher efficiency when close to the threshold that could be related to the increased series resistance maintaining FN as main electron injection mechanism. It must also be noted that the obtained threshold currents of single-layer devices are in accordance with the change in conduction observed at around 7 V.

So far, our results present a clear correlation between the emission and the conduction regime of the device. Considering electrons as majority carriers through the system (as suggested by the energy band diagrams in **Figure 3c and d**), the excitation mechanism of the RE ions must be related to their injection into the doped-ZnO layer. Electrons, under forward bias, are injected from the *n*-type Si substrate into the doped-ZnO layer by tunneling through the dielectric SiO<sub>x</sub> barrier, the difference in energy between the substrate and ZnO:RE conduction bands providing the carriers with additional energy. Below the threshold of FN injection, electrons gain enough energy to tunnel but are then trapped by ZnO inter-band gap traps, thus not being able to excite the rare earth ions. Under large applied voltage, these hot electrons might gain additional energy

due to the inclination of the ZnO conduction band and impact with the RE ions dispersed within the ZnO:RE layer, transferring their energy to excite the outer shell electrons of these elements, in a process called impact excitation.[29] Another (less probable) possibility includes a low injection of holes as minority carriers, creating an exciton. The energy of this particle could be transferred to the RE ions thanks to the lattice.[30] Their later relaxation results in the emission of photons we detect as EL emission. In contrast and as previously discussed, under reverse bias the injection of both electrons and holes is highly quenched, diminishing the possibility of RE excitation and resulting in no-observable EL emission.

EL emission from the devices is visible by the naked eye at high voltages. The insets in **Figure 4a** show pictures of this visible emission from the devices while being electrically excited (each picture is marked with a symbol that matches the graph legend). These were acquired by setting a standard photographic-digital camera focusing through the microscope and collecting the image for 30 s while applying 2 mA of constant current to the devices. Both ZnO:Ce and the multilayered ZnO:Ce/ZnO:Tb/ZnO:Eu,Tb devices show a weak emission mainly located close to the contact point of the tip, whereas the other two exhibit a more homogeneous and intense emission, in agreement with the previous observations of the integrated EL curves. Finally, regarding the EL color exhibited by each device, Ce-doped ones present a white-blueish emission, Tb-doped devices a clear green one, Eu,Tb-doped devices emit in orange-red. Finally, the multilayered devices present a white emission at the tip location.

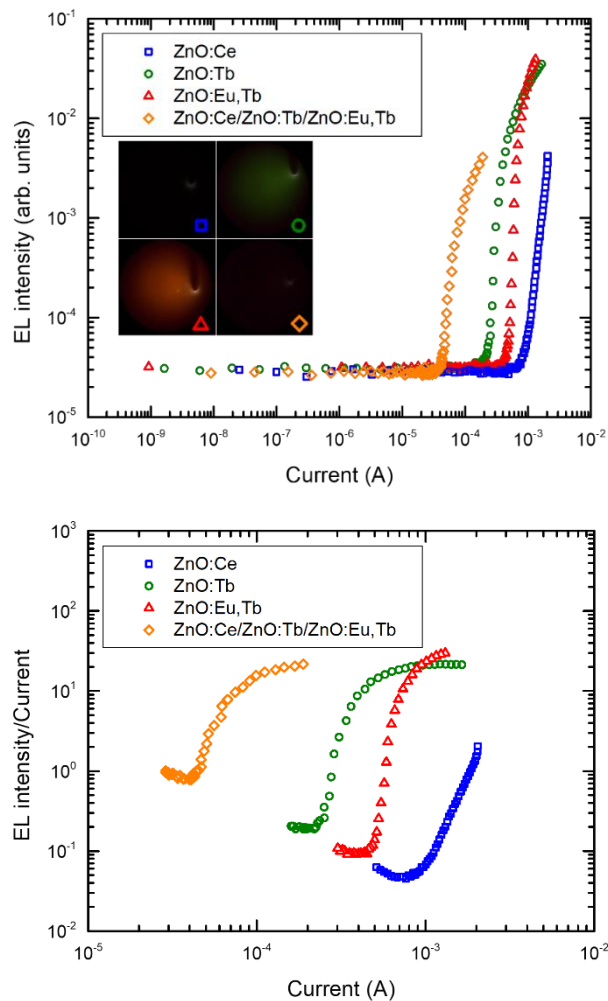

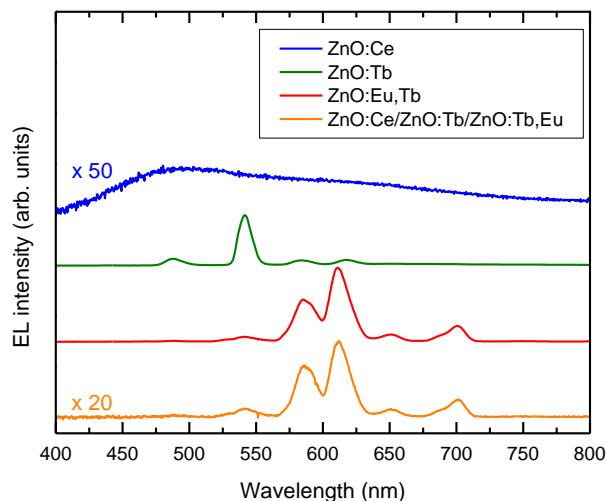

**Figure 4.** (a) Integrated electroluminescence of the four analyzed devices measured from 0 to 8 V. Pictures of the devices visible emission under electrical excitation are shown in the inset. (b) Representation of the integrated emission as emission efficiency, equivalent to an external quantum efficiency (EQE). (c) Corresponding electroluminescence spectra for the devices, collected during 30 seconds at 1 mA of applied current. Both graphs employ the same color code: ZnO:Ce in blue, ZnO:Tb in green, ZnO:Eu,Tb in red and ZnO:Ce/ZnO:Tb/ZnO:Eu,Tb in orange.

The representation of the EL intensity data as shown in [Figure 4b](#) allows comparing the devices in terms of their emission efficiency. Indeed, this representation is equivalent to the external quantum efficiency (EQE) of each device, that is, the amount of light extracted per injected electrons. The multilayer device is clearly identified as the more efficient out of the four when referring to their threshold of emission. Nevertheless, all devices present a fast increase in efficiency that is afterwards saturated, in accordance with electron injection following the FN regime previously identified. In the case of ZnO:Ce, this regime has not yet been reached, thus resulting in the very low efficiency measured.

Once the threshold current for EL to occur was determined, the excitation mechanism has been identified and there are evidences that the emission could be seen by the naked eye, spectral measurements were carried out on each device by applying a fixed excitation current of 1 mA in substrate accumulation conditions. This current value corresponds to  $\sim 8$  V, where the high-voltage conduction mechanisms are well established for each device. In [Figure 4c](#), the EL spectra for all four devices, measured under said conditions, are displayed.


Out of the three single-doped samples, ZnO:Ce shows a spectrum composed of two weak and wide features centered below 500 nm and around  $\sim 650$  nm, which would correspond to a combination of the electronic transitions listed in [Figure 1](#) for  $\text{Ce}^{3+}$  (421 and 464 nm) and the emission of ZnO defects, respectively. The broad emission band obtained instead of the well-defined electronic transitions is related to the electronic states delocalization because of orbital distortion, caused by  $\text{Ce}^{3+}$  ions clustering, as well as additional interactions with  $\text{Ce}^{4+}$  ions, which we have previously attributed to affect the electrical properties. [\[27,28\]](#) The combination of these two facts increases the probability of non-radiative processes taking place, thus diminishing the emission of the device. Oxidation of  $\text{Ce}^{3+}$  to  $\text{Ce}^{4+}$  is additionally supported by the appearance of the defects-related emission of ZnO, resulting from a larger concentration of oxygen vacancies in the film.

In contrast, both ZnO:Tb and ZnO:Eu,Tb devices show intense emission with narrow peaks corresponding to the electronic transitions of Tb<sup>3+</sup> and Eu<sup>3+</sup> (see [Figure 1](#)). The main emission of the Tb-doped sample is peaked at 541 nm, with three secondary peaks centered at 488 nm, 584 nm and 617 nm, all four features constituting the expected emission of Tb<sup>3+</sup> ions. [\[31–33\]](#) In the case of the ZnO:Eu,Tb device, other works in the literature have proved a higher efficiency of EL emission of Eu<sup>3+</sup> ions for the co-doped films when compared to a device only containing Eu. [\[31,34\]](#) Its EL exhibits its main emission peak at 611 nm, and three secondary peaks at 585 nm, 651 nm and 700 nm, which is in agreement with the Eu<sup>3+</sup> ions emission, [\[35\]](#) although Tb is also optically active. Notwithstanding, the emission of Tb<sup>3+</sup> ions appears to be quenched when compared to the emission of Eu<sup>3+</sup> ones. On one hand, the main emission of Tb<sup>3+</sup>, <sup>5</sup>D<sub>4</sub>→<sup>7</sup>F<sub>5</sub>, has a higher energy than the <sup>7</sup>F<sub>0</sub>→<sup>5</sup>D<sub>0</sub> excitation transition of Eu<sup>3+</sup> and thus the energy involved in this emission is partially transferred to Eu<sup>3+</sup> ions and converted into an Eu<sup>3+</sup> emission (the <sup>5</sup>D<sub>1</sub> and <sup>5</sup>D<sub>0</sub> electronic states might be populated). On the other hand, the remaining Tb<sup>3+</sup>-related emission is hidden by the emission of Eu<sup>3+</sup>, as some of the main contributions almost overlap in wavelength (see [Figure 1](#)). All these three emissions correspond well (in color and intensity) to the images of the devices shown in the insets of [Figure 4a](#).

In agreement with the emission of the single-doped samples, the fourth one, combining all three layers, shows the characteristic emission peaks of Tb<sup>3+</sup> and Eu<sup>3+</sup> in the same positions as previously observed. This fact indicates that the optical activity of RE ions is still preserved when sputtered on a stack structure. Tb<sup>3+</sup> ions emission can be detected by visually comparing the relative intensities between peaks at 541 nm and 611 nm with those in sample ZnO:Eu,Tb. Therefore, the layer sequence is optimal for obtaining a combined emission of the RE ions from one device, avoiding the Eu<sup>3+</sup> absorption of Tb<sup>3+</sup>-emitted photons that would take place if Eu was on top. Last, it is worth noting that the emission of the combined-RE stack is 20 times less intense (as indicated) than that of the previously commented devices, which is a consequence of the reduction in thickness of the two emitting layers (as discussed during the structural characterization), and the presence of ZnO:Ce on top quenching the emission from the bottom layers.

#### d. Chromatic diagram

To complement the electro-optical study carried out in this work, the resulting EL emission from the investigated devices was analyzed under the CIE 1931 standard for reference. The position of the four obtained spectra are displayed in the chromatic diagram in [Figure 5](#): ZnO:Ce corresponds to yellow due mainly to the emission of ZnO defects. Emission from ZnO:Tb and ZnO:Eu,Tb well correspond to green and red-orange colors in the diagram, respectively. In addition, the device containing the three different layers exhibits an orange color closer to the white center of the diagram, in agreement with the presence of both Tb<sup>3+</sup> and Eu<sup>3+</sup> emissions.

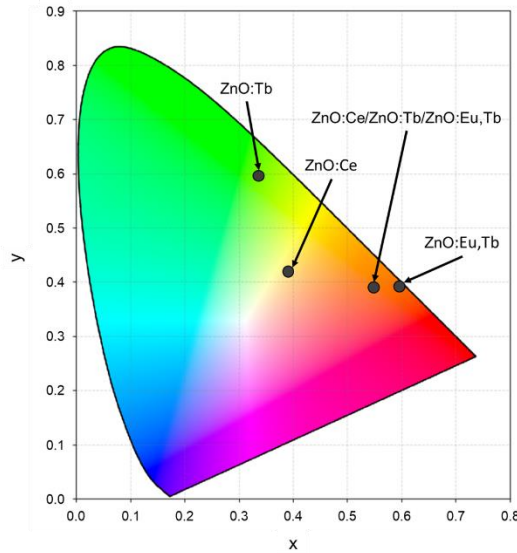

**Figure 5.** Location of the emission corresponding to each LED under study in the present work within the standard CIE 1931 chromatic diagram.

Indeed, from the chromatic diagram it becomes clear that blue emission from Ce ions has not yet been achieved or is highly quenched by the emission of ZnO-defects. If blue emission from  $\text{Ce}^{3+}$  could be added to the system, the position of the multilayered sample would become even closer to the center. Therefore, aiming at obtaining an efficient RE-based RGB LED, it is necessary to improve the deposition of a light-emitting  $\text{Ce}^{3+}$ -doped ZnO-based layer whose emission can provide the blue component expected to be combined with the intense green ( $\text{Tb}^{3+}$ ) and red ( $\text{Eu}^{3+}$ ) hereby already demonstrated.

## Conclusion

The devices hereby analyzed have proved the possibility of fabricating an RGB LED employing ZnO as host matrix for RE ions, using sputtering as the main deposition technique. For this purpose, three different RE elements have been explored, Ce, Tb and Eu, whose EL emission characteristics (determined by the electronic transitions when in a +3 valence state) respectively result in blue, green and red intense and narrow emissions.

Out of the three,  $\text{Tb}^{3+}$  and  $\text{Eu}^{3+}$  are optically active after the deposition and annealing processes underwent to achieve the device structure, and under the electrical excitation conditions employed for attaining EL devices emission; instead, Ce has only shown poor EL emission and only under high stress conditions. The analysis and characterization via TEM and EDX, as well as the electrical conduction mechanisms analysis, point towards the agglomeration of Ce ions in the layer to be larger than in the case of Tb and Eu, affecting their local stoichiometry and therefore carrier transport and emission properties. Nonetheless, the results for Ce are still promising, and future test and characterization of the ZnO:Ce films controlling Ce-concentration and distribution are expected to improve their EL efficiency. The stack fabrication of the three films into a single device has also been tested, enabling the emission of the different optically-active centers present within the whole structure. As intended, their combined emission is shifted, with respect to the emission of the single layered devices, towards the central region of the chromatic diagram.

Overall, the hereby presented results reinforce the suitability of ZnO as an adequate matrix to host optically-active RE ions with intense and narrow emission, useful for fabricating full-color light sources for general lighting and other optoelectronics applications.

## Acknowledgements

This work was financially supported by the Spanish Ministry of Economy and Competitiveness (Project No. TEC2016-76849-C2-1-R). J.L.F. acknowledges the subprogram “Ayudas para la Formación de Profesorado Universitario” (No. FPU16/06257) from the Spanish Ministry of Education, Culture and Sports for economical support. J.L.-V. acknowledges financial support from a “Juan de la Cierva” postdoctoral fellowship (IJCI-2017-33451) from the Spanish Ministry of Economy, Industry and Competitiveness. X.P., C.L., and C.G. are grateful to C. Frilay for his expertise in the maintenance of the sputtering setup used for the growth of the ZnO films. They also thank F Lemarié for the TEM sample preparation by FIB.

## References

- [1] Özgür Ü, Alivov Y I, Liu C, Teke A, Reshchikov M A, Doğan S, Avrutin V, Cho S J and Morkoç H 2005 A comprehensive review of ZnO materials and devices *J. Appl. Phys.* **98** 1–103
- [2] Klingshirn C F 2007 ZnO: Material, physics and applications *ChemPhysChem* **8** 782–803
- [3] Rogers D J, Teherani F H, Sandana V E and Razeghi M 2010 ZnO thin films and nanostructures for emerging optoelectronic applications *Optoelectronic Integrated Circuits XII* vol 7605, ed L A Eldada and E-H Lee (SPIE) p 76050K
- [4] Laube J, Nübling D, Beh H, Gutsch S, Hiller D and Zacharias M 2016 Resistivity of atomic layer deposition grown ZnO: The influence of deposition temperature and post-annealing *Thin Solid Films* **603** 377–81
- [5] Chen X L, Wang F, Geng X H, Zhang D K, Wei C C, Zhang X D and Zhao Y 2012 Natively textured surface Al-doped ZnO-TCO layers with gradual oxygen growth for thin film solar cells via magnetron sputtering *Appl. Surf. Sci.* **258** 4092–6
- [6] Rahman F 2019 Zinc oxide light-emitting diodes: a review *Opt. Eng.* **58** 1
- [7] Prucnal S, Wu J, Berencén Y, Liedke M O, Wagner A, Liu F, Wang M, Rebohle L, Zhou S, Cai H and Skorupa W 2017 Engineering of optical and electrical properties of ZnO by non-equilibrium thermal processing: The role of zinc interstitials and zinc vacancies *J. Appl. Phys.* **122**
- [8] Janotti A and Van De Walle C G 2009 Fundamentals of zinc oxide as a semiconductor *Reports Prog. Phys.* **72** 126501
- [9] Fan J C, Sreekanth K M, Xie Z, Chang S L and Rao K V 2013 p-Type ZnO materials: Theory, growth, properties and devices *Prog. Mater. Sci.* **58** 874–985
- [10] Kenyon A J 2002 Recent developments in rare-earth doped materials for optoelectronics *Prog. Quantum Electron.* **26** 225–84
- [11] Khan L U and Khan Z U 2018 Rare earth luminescence: Electronic spectroscopy and applications *Handbook of Materials Characterization* (Cham: Springer International Publishing) pp 345–404

- [12] Gaponenko N V., Sergeev O V., Borisenko V E, Pivin J C, Skeldon P, Thompson G E, Hamilton B, Misiewicz J, Bryja L, Kudrawiec R, Stupak A P and Stepanova E A 2001 Terbium photoluminescence in polysiloxane films *Mater. Sci. Eng. B Solid-State Mater. Adv. Technol.* **81** 191–3
- [13] Heikenfeld J, Garter M, Lee D S, Birkhahn R and Steckl A J 1999 Red light emission by photoluminescence and electroluminescence from Eu-doped GaN *Appl. Phys. Lett.* **75** 1189–91
- [14] Luo Q, Wang L S, Guo H Z, Lin K Q, Chen Y, Yue G H and Peng D L 2012 Blue luminescence from Ce-doped ZnO thin films prepared by magnetron sputtering *Appl. Phys. A Mater. Sci. Process.* **108** 239–45
- [15] Anand V, Sakthivelu A, Kumar K D A, Valanarasu S, Ganesh V, Shkir M, Kathalingam A and AlFaify S 2018 Novel rare earth Gd and Al co-doped ZnO thin films prepared by nebulizer spray method for optoelectronic applications *Superlattices Microstruct.* **123** 311–22
- [16] Komuro S, Katsumata T, Morikawa T, Zhao X, Isshiki H and Aoyagi Y 2000 1.54 Mm Emission Dynamics of Erbium-Doped Zinc-Oxide Thin Films *Appl. Phys. Lett.* **76** 3935–7
- [17] Llusà M, López-Vidrier J, Antony A, Hernández S, Garrido B and Bertomeu J 2014 Up-conversion effect of Er- and Yb-doped ZnO thin films *Thin Solid Films* **562** 456–61
- [18] Röder R, Geburt S, Zapf M, Franke D, Lorke M, Frauenheim T, da Rosa A L and Ronning C 2019 Transition Metal and Rare Earth Element Doped Zinc Oxide Nanowires for Optoelectronics *Phys. Status Solidi Basic Res.* **256** 1–12
- [19] Ishii M, Komuro S, Morikawa T and Aoyagi Y 2001 Local structure analysis of an optically active center in Er-doped ZnO thin film *J. Appl. Phys.* **89** 3679–84
- [20] Li J, Zalloum O H Y, Roschuk T, Heng C L, Wojcik J and Mascher P 2008 Light emission from rare-earth doped silicon nanostructures *Adv. Opt. Technol.* **2008**
- [21] Umamaheswari D, Jamalajah B C, Sasikala T, Chengaiah T, Kim I G and Rama Moorthy L 2012 Photoluminescence and decay behavior of Tb 3+ ions in sodium fluoroborate glasses for display devices *J. Lumin.* **132** 1166–70
- [22] Sorokina I T 2007 Crystalline Mid-Infrared Lasers *Solid-State Mid-Infrared Laser Sources* vol 351 (Berlin, Heidelberg: Springer Berlin Heidelberg) pp 262–358
- [23] Jovanović D J, Antić Ž, Krsmanović R M, Mitrić M, Crossed D Signorcrossed D Signević V, Bártová B and Dramićanin M D 2013 Annealing effects on the microstructure and photoluminescence of Eu 3+-doped GdVO<sub>4</sub> powders *Opt. Mater. (Amst).* **35** 1797–804
- [24] Polman A 1997 Erbium implanted thin film photonic materials *J. Appl. Phys.* **82** 1–39
- [25] Takahei K, Taguchi A, Horikoshi Y and Nakata J 1994 Atomic configuration of the Er-O luminescence center in Er-doped GaAs with oxygen codoping *J. Appl. Phys.* **76** 4332–9
- [26] Ford G M and Wessels B W 1996 1.54 μm Electroluminescence From Erbium Doped Gallium Phosphide Diodes *Mater. Res. Soc. Symp. - Proc.* **422** 345–50
- [27] He X, Liu X, Li R, Yang B, Yu K, Zeng M and Yu R 2016 Effects of local structure of Ce<sup>3+</sup> ions on luminescent properties of Y<sub>3</sub>Al<sub>5</sub>O<sub>12</sub>:Ce nanoparticles *Sci. Rep.* **6** 1–11

- [28] Mishra S, Kshatri D S, Khare A, Tiwari S and Dwivedi P K 2016 SrS:Ce<sup>3+</sup> thin films for electroluminescence device applications deposited by electron-beam evaporation deposition method *Mater. Lett.* **183** 191–6
- [29] Ramírez J M, Ferrarese Lupi F, Jambois O, Berencén Y, Navarro-Urrios D, Anopchenko A, Marconi A, Prtljaga N, Tengattini A, Pavesi L, Colonna J P, Fedeli J M and Garrido B 2012 Erbium emission in MOS light emitting devices: From energy transfer to direct impact excitation *Nanotechnology* **23** 125203
- [30] Luo L, Huang F Y, Guo G J, Tanner P A, Chen J, Tao Y T, Zhou J, Yuan L Y, Chen S Y, Chueh Y L, Fan H H, Li K F and Cheah K W 2012 Efficient doping and energy transfer from ZnO to Eu<sup>3+</sup> ions in Eu<sup>3+</sup>-doped ZnO nanocrystals *J. Nanosci. Nanotechnol.* **12** 2417–23
- [31] Davesne C, Ziani A, Labbé C, Marie P, Frilay C and Portier X 2014 Energy transfer mechanism between terbium and europium ions in zinc oxide and zinc silicates thin films *Thin Solid Films* **553** 33–7
- [32] Blázquez O, López-Vidrier J, López-Conesa L, Busquets-Masó M, Estradé S, Peiró F, Hernández S and Garrido B 2016 Structural and optical properties of Al-Tb/SiO<sub>2</sub> multilayers fabricated by electron beam evaporation *J. Appl. Phys.* **120** 135302
- [33] Frieiro J L, Blázquez O, López-Vidrier J, López-Conesa L, Estradé S, Peiró F, Ibáñez J, Hernández S and Garrido B 2018 Green Electroluminescence of Al/Tb/Al/SiO<sub>2</sub> Devices Fabricated by Electron Beam Evaporation *Phys. status solidi* **215** 1700451
- [34] Borkovska L V., Khomenkova L, Korsunskaya O, Kolomys O, Strelchuk V, Sabov T, Venger E, Kryshchuk T, Melnichuk O, Melnichuk L, Guillaume C, Labbe C and Portier X 2019 Influence of annealing on luminescence and energy transfer in ZnO multilayer structure co-doped with Tb and Eu *Thin Solid Films* **692** 137634
- [35] Petersen J, Brimont C, Gallart M, Schmerber G, Gilliot P, Ulhaq-Bouillet C, Rehspringer J L, Colis S, Becker C, Slaoui A and Dini A 2010 Correlation of structural properties with energy transfer of Eu-doped ZnO thin films prepared by sol-gel process and magnetron reactive sputtering *J. Appl. Phys.* **107** 1–7