



HAL
open science

Impact of La Concentration on Ferroelectricity of La-Doped HfO₂ Epitaxial Thin Films

T. Song, H. Tan, Romain Bachelet, Guillaume Saint-Girons, I. Fina, F.
Sánchez

► **To cite this version:**

T. Song, H. Tan, Romain Bachelet, Guillaume Saint-Girons, I. Fina, et al.. Impact of La Concentration on Ferroelectricity of La-Doped HfO₂ Epitaxial Thin Films. ACS Applied Electronic Materials, 2021, 3 (11), pp.4809-4816. 10.1021/acsaelm.1c00672 . hal-03622064

HAL Id: hal-03622064

<https://hal.science/hal-03622064>

Submitted on 5 Apr 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution 4.0 International License

Impact of La Concentration on Ferroelectricity of La-Doped HfO₂ Epitaxial Thin Films

Tingfeng Song, Huan Tan, Romain Bachelet, Guillaume Saint-Girons, Ignasi Fina,* and Florencio Sánchez*



Cite This: *ACS Appl. Electron. Mater.* 2021, 3, 4809–4816



Read Online

ACCESS |



Metrics & More




Article Recommendations



Supporting Information

ABSTRACT: Epitaxial thin films of HfO₂ doped with La have been grown on SrTiO₃(001) and Si(001), and the impact of the La concentration on the stabilization of the ferroelectric phase has been determined. Films with 2–5 at. % La doping present the least amount of paraelectric monoclinic and cubic phases and exhibit the highest polarization, having a remanent polarization above 20 $\mu\text{C}/\text{cm}^2$. The dopant concentration results in an important effect on the coercive field, which is reduced with increasing La content. Combined high polarization, high retention, and high endurance of at least 10¹⁰ cycles is obtained in 5 at. % La-doped films.

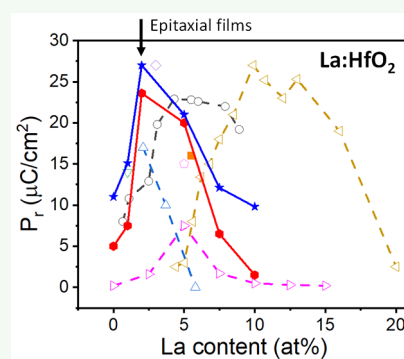

KEYWORDS: ferroelectric HfO₂, ferroelectric oxides, epitaxial HfO₂, epitaxial oxides on silicon, thin films

1. INTRODUCTION

Ten years after the first report on ferroelectricity in doped HfO₂, this material is receiving a huge interest from the academy and industry. Most of the progress has been made by investigating polycrystalline films,^{1–7} and recently epitaxial films are also contributing.^{8–15} A significant number of chemical elements are used as dopant to stabilize the ferroelectric phase in polycrystalline HfO₂. The most investigated chemical composition is Hf_{0.5}Zr_{0.5}O₂.¹⁶ Recently, attention is being paid to large radius dopant atoms, particularly La, and high values of polarization and endurance have been reported.⁵ Moreover, robust ferroelectricity has been demonstrated in 1 μm thick La:HfO₂ films.¹⁷

The dependence of the polarization of La:HfO₂ films on the La content is reported in few papers, which are focused in polycrystalline films and with big difference in the determined optimal La content. Chernikova et al.¹⁸ grew by plasma-enhanced atomic layer deposition films of thickness $t = 10$ nm with La content ranging from 2.1 to 5.8 at. % and measured the highest remanent polarization ($P_r = 17 \mu\text{C}/\text{cm}^2$) in the 2.1 atom % film. Schroeder et al.¹⁹ used atomic layer deposition (ALD) to grow $t = 10$ nm films with a wide range of La content from 4.4 to 34 at. % and reported the highest P_r (27 $\mu\text{C}/\text{cm}^2$) for a content of around 10 at. %. More recently, Mart et al.²⁰ prepared by ALD $t = 10$ nm films with La content from less than 1 to more than 8 at. %, measuring the largest P_r (23 $\mu\text{C}/\text{cm}^2$) in films with a La concentration of around 5.5 at. %. TiN was used as bottom and top electrode in these studies. In contrast, Schenk et al.¹⁷ prepared $t = 45$ nm La:HfO₂ films (La


content ranging from 0 to 15 at. %) by chemical solution deposition using bottom and top Pt electrodes, and they reported the maximum P_r (7 $\mu\text{C}/\text{cm}^2$) for films with a La content of 5 at. %. The dispersion in the reported results suggests that the optimal content of La depends on the thin film deposition technique and growth parameters, as noted by Materlik et al.²¹ Indeed, distinct deposition techniques and processing parameters result in different amount of oxygen vacancies, which has an impact on the crystallization of the competing polymorphs.⁷

In contrast to polycrystalline samples, epitaxial La:HfO₂ films have been very scarcely investigated,^{22,23} and the effect of the La content on the ferroelectric properties has not been addressed. To investigate it, we have prepared a series of La:HfO₂ films with varied La content (0, 1, 2, 5, 7.5, and 10 at. %) deposited on (001)-oriented SrTiO₃ (STO) and Si substrates. We present here characterization of the crystal phases and surface morphology and detailed electrical measurements that include polarization loops, leakage current, and permittivity loops. The impact of the La content on the crystal phases and the electrical properties is determined. The

Received: July 27, 2021

Accepted: September 28, 2021

Published: October 19, 2021



remanent polarization is the largest for La content of 2–5 at. %, and the coercive field decreases with La content. As a result of these dependences, a La concentration of 5 at. % allows a high endurance of more than 10^{10} cycles with good retention properties.

2. EXPERIMENTAL SECTION

La:HfO₂ films and bottom La_{0.67}Sr_{0.33}MnO₃ (LSMO) electrodes were grown on STO(001) substrates in a single process by pulsed laser deposition (PLD) using a KrF excimer laser. Hf_{1-x}La_xO_{2-δ} ($x = 0, 0.01, 0.02, 0.05, 0.075, \text{ and } 0.1$) and La_{0.67}Sr_{0.33}MnO₃ sintered pellets of 1 in. diameter were used as targets. LSMO electrodes of thickness around 25 nm were grown at a substrate temperature $T_s = 700$ °C, an oxygen pressure $P_{O_2} = 0.1$ mbar, and a laser frequency of 5 Hz and have an electrical resistivity ~ 1 mΩ·cm. The corresponding parameters used to grow La:HfO₂ films of thickness around 8.5 nm were $T_s = 800$ °C, $P_{O_2} = 0.1$ mbar, and 2 Hz. An equivalent series of La:HfO₂/LSMO bilayers were grown on Si(001) wafers (p-type, resistivity 1–10 Ω·cm) buffered with epitaxial STO films deposited *ex situ* by molecular beam epitaxy (MBE). Details of MBE deposition of the STO buffers are reported elsewhere.^{24,25} Platinum circular top electrodes, of thickness 20 nm and diameter 20 μm, were deposited *ex situ* by sputtering through stencil masks for electrical characterization. Figures 1a and 1b show sketches of the Pt/La:HfO₂/LSMO heterostructures on STO(001) and STO/Si(001), respectively.

X-ray diffraction (XRD) with Cu Kα radiation was used to study the crystal structure. A Siemens D5000 and a Bruker D8-Discover equipped with a point detector and a Bruker D8-Advance equipped with a 2D detector diffractometer were used. A Keysight 5100 atomic force microscope (AFM) was used in dynamic mode to investigate the surface topography.

An AixACCT TFAnalyser2000 platform was used to measure ferroelectric polarization loops, current leakage, retention, and endurance at room temperature (except for some retention measurements performed at 85 °C). Measurements were done connecting the LSMO bottom electrode to the ground and biasing the top Pt contact. Ferroelectric polarization loops were obtained in dynamic leakage current compensation (DLCC) and positive-up negative-down (PUND) modes with a frequency of 1 kHz. Endurance was evaluated by using bipolar square pulses and measuring the loops by DLCC. Capacitance (C) loops were measured by using an impedance analyzer (HP4192LF, Agilent Co.) operated with an excitation voltage of 0.3 V at 50 kHz. Relative dielectric permittivity (ϵ_r)–voltage loops were extracted from capacitance values by using the $C = \epsilon_0 \epsilon_r A/t$ relation, where A is the electrode area and t is the film thickness. Retention measurements were done by poling the sample (triangular pulse, 0.25 ms), measuring polarizations loops at 1 kHz by using the PUND protocol after a delay time, and determining the P_r from the first polarization curve (as described in the Supporting Information S1 and in ref 11).

3. RESULTS

XRD 2θ – χ maps (Figure 1c) show bright spots at $\chi = 0^\circ$. The spots at $2\theta \sim 23^\circ$ and $\sim 47^\circ$ correspond to (001) and (002) reflections of the STO substrate overlapped to the LSMO electrode reflection. The other spots correspond to La:HfO₂ reflections. The spots at $2\theta \sim 28.3^\circ$ and $\sim 34.4^\circ$ are at the positions of the (–111) and {200} reflections, respectively, of the monoclinic (m) phase (space group number 14, $P2_1/c$). The maps of all films show a spot at $2\theta \sim 30^\circ$, where the (111) reflection of the orthorhombic (o) phase (61, $Pbca$), the (111) reflection of the cubic (c) phase (225, $Fm\bar{3}m$), and the (101) reflection of the tetragonal (t) phase (137, $P4_2/nmc$) are located. In polycrystalline La:HfO₂ films, the orthorhombic and cubic phases generally stabilize with moderately low and high La content, respectively.^{18,19} Here, for the sake of

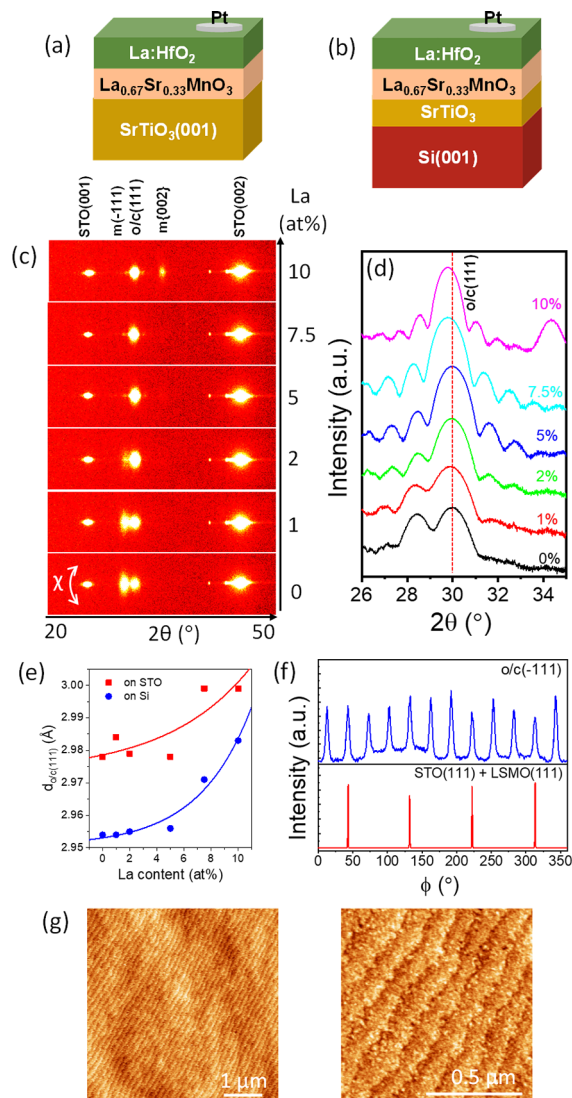


Figure 1. Sketches of the Pt/La:HfO₂/LSMO heterostructures on STO(001) (a) and STO/Si(001) (b). XRD 2θ – χ maps (c) and θ – 2θ scans (d) of the La:HfO₂ films on STO(001). (e) Out-of-plane lattice parameter associated with the o/c(111) reflection as a function of the La concentration for films on STO(001) (red squares) and Si(001) (blue circles). Lines are guides for the eye. (f) XRD ϕ -scans, measured in the 2 at. % La film on STO(001), around o/c(–111) reflections (top panel) and STO(111)/LSMO(111) reflections. (g) Topographic AFM images of the 2 at. % La film on STO(001), scanned in $5 \mu\text{m} \times 5 \mu\text{m}$ (left panel) and $1 \mu\text{m} \times 1 \mu\text{m}$ (right panel) regions.

simplicity, the spot at $2\theta \sim 30^\circ$ is indexed as o/c(111). The 2θ – χ map of the undoped HfO₂ film (0 at. % La) shows a bright m(–111) spot while the m{200} reflections are not detected. In films with a concentration of La 1 and 2 at. %, the intensity of the m(–111) spot decreases with increasing La content, and the m{200} spot is barely visible. The m(–111) spot is not detected in films with higher La content, but a m{200} spot is clearly observed in the 10 at. % La film. XRD θ – 2θ scans measured with a point detector are shown in Figure 1d. There are Laue oscillations around the reflection at $2\theta \sim 30^\circ$. The films thickness and the out-of-plane lattice parameter corresponding to this reflection were determined from the simulation of the Laue oscillations (Supporting Information S2). The films are around 8 nm thick, except the 10 at. % film

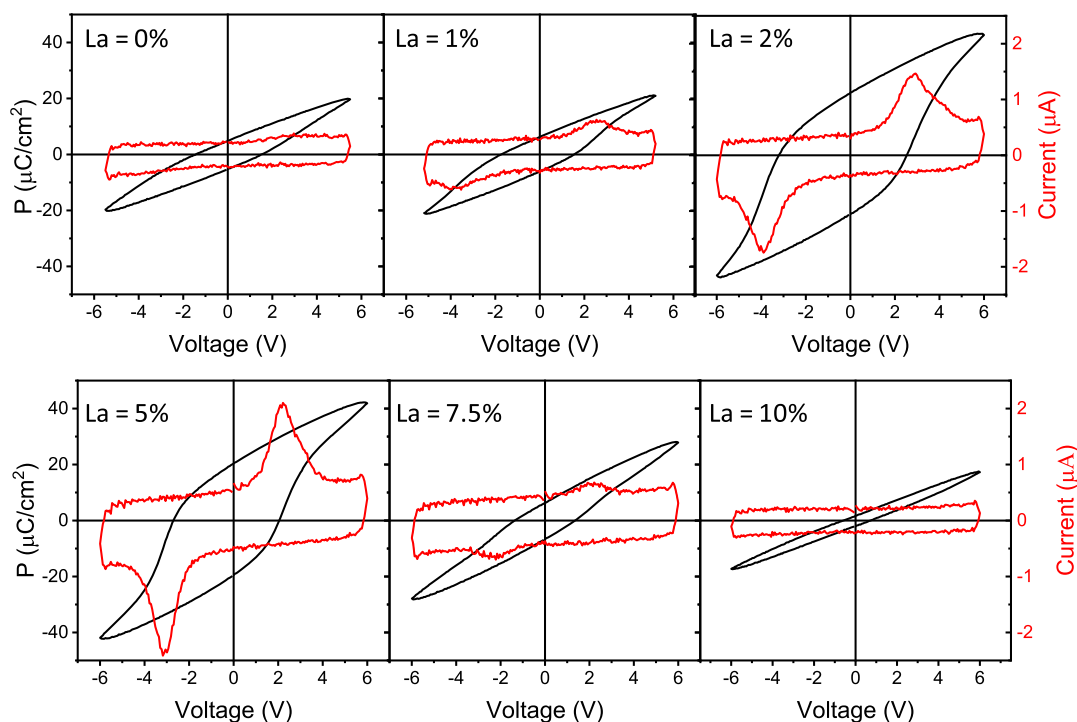


Figure 2. Current–voltage curves (red lines) and polarization loops (black lines) of the series of La:HfO₂ films on STO(001). The La concentration is indicated in the label at the top left of each panel.

which is 10.5 nm thick. The $d_{o/c(111)}$ values are ~ 2.98 Å in the Hf_{1-x}La_xO_{2-δ} films with x up to 0.05 and slightly expanded, ~ 3.0 Å, in the $x = 0.075$ and $x = 0.1$ films (Figure 1e). The $d_{o/c(111)}$ elongation in La-rich films could signal an increased fraction of cubic phase in these films, as it has been observed in polycrystalline films.¹⁸ The XRD characterization of the equivalent series of films on Si(001) is summarized in Supporting Information S3. The θ - 2θ scans show that the o/c(111) peak in all films is accompanied by a strong m(-111) peak in the pure HfO₂ film and a low-intensity m{200} peak in the other samples. The $d_{o/c(111)}$ out-of-plane lattice parameter shows a dependence on La content similar to that of films on STO(001) with lattice expansion in the La-rich films (Figure 1e). However, for a fixed La content, the $d_{o/c(111)}$ parameter of the film on Si(001) is smaller than that of the corresponding film on STO(001). Similar shrinkage occurs in other doped-HfO₂ epitaxial films on Si(001) and is considered an effect of the tensile stress caused by the Si(001) substrate. Si has a low thermal expansion coefficient, and this produces a tensile stress on the film when it is cooled after growth at high temperature.^{26,27}

The ϕ -scans shown in Figure 1f confirm that the La:HfO₂ films are epitaxial, presenting the same epitaxial relationship with the STO(001) substrate than other doped HfO₂ epitaxial films grown on either perovskite or Si(001) substrates.^{25,28,29} Moreover, topographic AFM images (Figure 1g) confirm that the films are very flat, with morphology of terraces and steps and low root-mean-square roughness (rms) of around 1.5 Å. Topographic AFM images of the complete series of films with varying La concentration are shown in Supporting Information S4. All films are very flat, although terraces are barely visible in the 10 at. % film, and the rms roughness increases to 3.7 Å. The La:HfO₂ films on STO/Si(001) are also very flat, with rms roughness around 2 Å (Supporting Information S5).

Figure 2 shows current–voltage curves (red lines) and polarization loops (black lines) of the films on STO(001), measured in the pristine state by the DLCC method. The switching peaks in the current–voltage curve of the pure HfO₂ film are small, and remanent polarization (P_r) is < 5 $\mu\text{C}/\text{cm}^2$. The amplitude of the ferroelectric switching peaks and the resulting polarization become greater with increasing La concentration, with P_r particularly high in the 2 at. % La ($P_r \sim 22$ $\mu\text{C}/\text{cm}^2$) and 5 at. % La ($P_r \sim 20$ $\mu\text{C}/\text{cm}^2$) films. The polarization decreases in the films with a higher amount of La, being $P_r \sim 6.5$ $\mu\text{C}/\text{cm}^2$ in the 7.5 at. % La film, while the 10 at. % La film does not show ferroelectric switching peaks. PUND measurements confirmed the enhancement of ferroelectric polarization in the films with La concentration 2–5 at. % (Supporting Information S6). The polarization of the films on Si(001) shows a similar dependence on the La concentration, with P_r above 25 and 20 $\mu\text{C}/\text{cm}^2$ in the 2 and 5 at. % films, respectively (Supporting Information S7). Piezoelectric force microscopy characterization of the 2 and 5% doped samples (Supporting Information S8) also shows a ferroelectric response.

Figure 3 shows the dependence of the remanent polarization of the epitaxial films on STO(001) (solid red rhombi) and Si(001) (solid blue diamonds) on the La concentration. The concentration of La that maximizes the polarization in the epitaxial films is seen to be in the range 2–5 at. %. The polarization of the 2 at. % epitaxial films is larger when the film thickness is < 7 nm.²³ On the other hand, the polarization reported by Li et al.²² for a $t = 12$ nm epitaxial 5.5 at. % film (solid orange square) fits well to our data. Figure 3 also includes data reported for series of polycrystalline films. The dependences on the La concentration for the polycrystalline films reported by Chernikova et al.¹⁸ (open blue triangles) and Schenk et al.¹⁷ (open pink triangles) do not differ greatly from the epitaxial films. In contrast, the data reported by Mart et

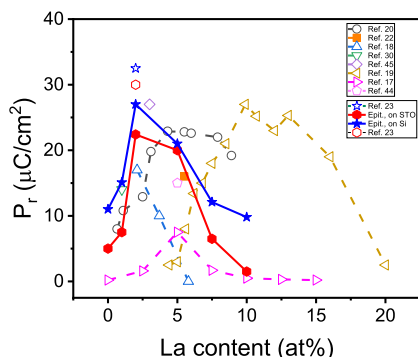


Figure 3. Dependence of the remanent polarization with the La concentration of the epitaxial films on STO(001) (solid red diamonds) and Si(001) (solid blue stars). The empty red diamond and empty blue star correspond to 2 at. % $t = 6.9$ nm epitaxial films grown by using same conditions on STO(001) and Si(001), respectively.²³ The remanent polarization of a $t = 12$ nm epitaxial film on STO(001) reported by Li et al.²² is indicated by a solid orange square. Data of series of polycrystalline films with varied La concentration are shown with open gray circles ($t = 10$ nm),²⁰ open up blue triangles ($t = 10$ nm),¹⁸ open pink right triangles ($t = 45$ nm),¹⁷ and open gold left triangles ($t = 10$ nm).¹⁹ Other reported data of polycrystalline films with fixed La concentration are indicated by open pink pentagon ($t = 45$ nm)⁴⁴ and open violet diamond ($t = 50$ nm).⁴⁵

al.²⁰ (open gray circles) and particularly by Schroeder et al.¹⁹ (open gold triangles) point to a greater amount of La having the largest polarization. This can be due to the combined effect of several factors, including the possibility of La segregation depending on the preparation conditions. Because epitaxial films are closer to intrinsic HfO₂ than polycrystalline films, a concentration of 2–5 at. % is estimated to be optimal to stabilize the ferroelectric phase in La-doped HfO₂.

The concentration of La has a great effect not only on polarization but also on the coercive field (E_C). Figure 4 (round symbols) shows the E_C dependence of the films on STO(001) with the La concentration, determined from the

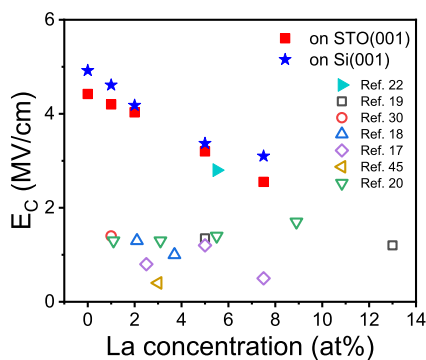


Figure 4. Coercive electric field dependence of La concentration for epitaxial films on STO(001) (solid red squares) and Si(001) (solid blue stars). Values were determined from the current peak position on the current–voltage curves measured by DLCC. The solid right green triangle indicates the E_C value reported for an epitaxial $t = 12$ nm film.²² Open symbols indicate reported E_C values for polycrystalline films: open black squares,¹⁹ open red circle,³⁰ open up blue triangles,¹⁸ open purple diamonds,¹⁷ open left gold triangle,⁴⁵ and open down green triangles.²⁰ Values from ref 20 were taken from Figure 3b, and only the current peaks of greater amplitude in the films showing double peaks were considered.

peak position in current–voltage curves (Figure 2). The films have a larger coercive field than La-doped HfO₂ polycrystalline films.^{18–20,30} This is in accordance with the usual high coercive field of epitaxial films of HfO₂ doped with different atoms.⁸ The possibility of selecting E_C is of enormous interest, since it could allow to enhance the endurance. Thus, the monotonic decrease of E_C from 4.42 to 2.55 MV/cm with the concentration of La is remarkable. The same dependence is observed in the films on Si(001), with a decrease in E_C from 4.92 to 3.1 MV/cm (Figure 4, star symbols). The E_C value of an epitaxial La:HfO₂ film on STO(001) reported by another group (solid right green triangle)²² fits very well with the E_C –La content dependence of our epitaxial films. The decrease of the E_C of the epitaxial films with the increase in La content could be due to a greater number of defects that would facilitate domain switching.¹⁹ The E_C values of most polycrystalline films range from 0.5 to 1.7 MV/cm (Figure 4, empty symbols), without a clear dependence on La content. Schroeder et al.¹⁹ noted a slight decrease in E_C with La concentration (Figure 4, for simplicity, shows only two of the reported values). More recently, they have reported³¹ $E_C \sim 3$ MV/cm in $t = 10$ nm polycrystalline La:HfO₂ films.

Figure 4 shows a clear dependence of E_C with the concentration of La for epitaxial films and a great dispersion for the polycrystalline films. The defects present in polycrystalline films, expected in greater quantity than in epitaxial films, can be a main factor decreasing the E_C and causing dispersion.³² Polycrystalline films of HfO₂ doped with different atoms tend to have a lower E_C compared to the equivalent epitaxial films.^{6,8} Furthermore, $E_C \sim t^{-2/3}$ scaling is reported for epitaxial films,^{8,23,33} but it has rarely been observed with polycrystalline films. An exception, recently reported by Materano et al.,³¹ shows a strong dependence of the coercive field of polycrystalline HZO and La:HfO₂ (the concentration of La is not indicated) on thickness of the film and the grain size. The E_C values were very high, and the comparison with equivalent epitaxial HZO³³ and La:HfO₂²³ (Supporting Information S9) evidences (1) the polycrystalline films (HZO and La:HfO₂)³¹ exhibit $E_C \sim t^{-2/3}$ scaling and have E_C values similar to epitaxial films of the same thickness and (2) E_C values are slightly higher in La:HfO₂ than in films of HZO of the same thickness. The leakage curves of the films on STO(001) and Si(001) are shown in Figures 5a and 5b, respectively. The pure HfO₂ film (0 at. % La) on STO(001) exhibits leakage current of $\sim 5 \times 10^{-6}$ and $\sim 5 \times 10^{-7}$ A/cm² at 2 and 1 V, respectively. In the doped films, leakage decreases down to $\sim 1 \times 10^{-6}$ A/cm² (at 2 V) and $\sim 2 \times 10^{-7}$ A/cm² (at 1 V) with La concentration >1 at. % (Figure 5c). The current leakage values are similar to those commonly reported in doped HfO₂ polycrystalline films of similar thickness.³⁴ However, they are high compared to the extremely low leakage current of $\sim 10^{-8}$ A/cm² at 2 MV/cm that has been reported in polycrystalline films of TiN/La:HZO/TiN on Si(001).³⁵ Epitaxial La:HfO₂ films on Si(001) show a similar dependence (Figure 5d) than on STO(001), although the leakage current, particularly at high voltage, is greater than in the equivalent films on STO(001). Similarly larger leakage current in epitaxial doped HfO₂ films on STO-buffered Si(001) was previously reported.^{23,36} Leakage is measured by applying rather long voltage pulses (around 1 s), and ionic current at grain boundaries may be a relevant contribution.^{37,38} The higher leakage of films on Si(001) could be due to

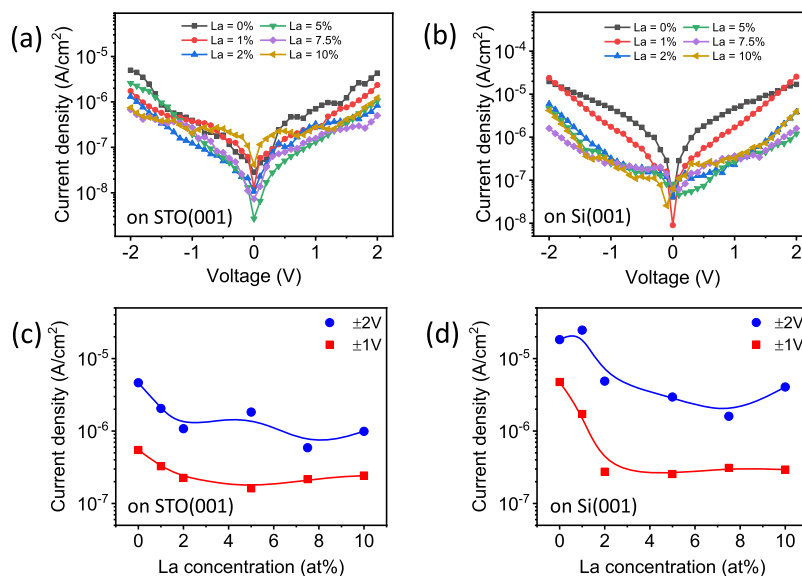


Figure 5. Current leakage curves of the films on STO(001) (a) and Si(001) (b). Dependence of the current leakage at 1 V (red squares) and 2 V (blue circles) on the La concentration in films on STO(001) (c) and Si(001) (d). The current leakage values in (b) and (c) are the average values at positive and negative bias.

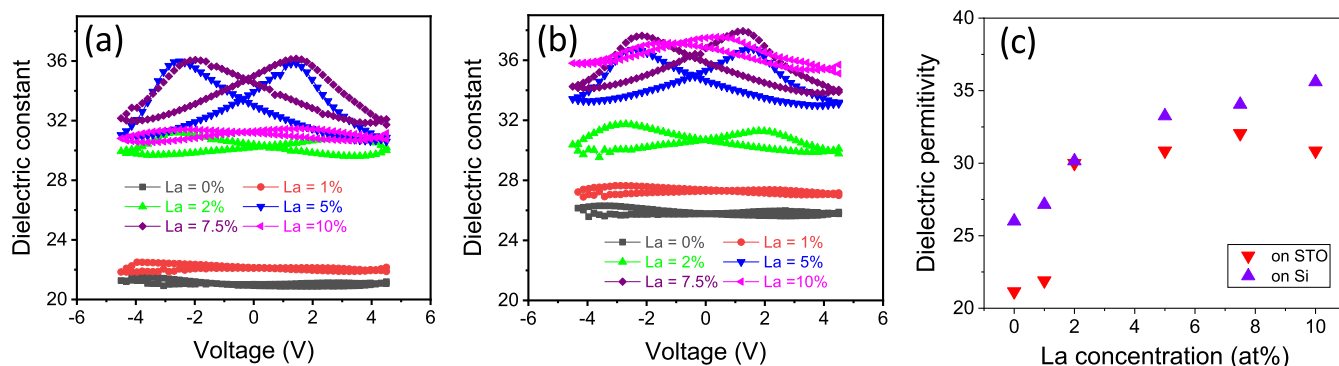


Figure 6. Dielectric constant loops of the films on STO(001) (a) and Si(001) (b). (c) Dependence of the dielectric constant at high field (average values at positive and negative bias) on the La concentration of films on STO(001) (red down triangles) and Si(001) (top blue triangles).

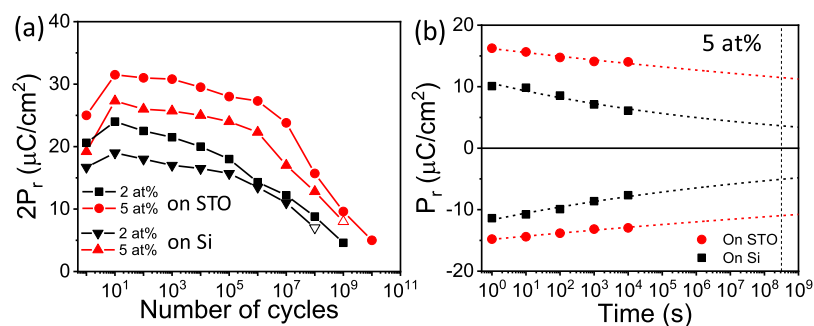


Figure 7. (a) Polarization window ($2P_r$) as a function of the number of bipolar cycles of amplitude 5 V of films on STO(001) with La concentration 2 at. % (black squares) and 5 at. % (red circles) and 4.5 V of films on Si(001) with La concentration 2 at. % (black down triangles) and 5 at. % (red up triangles). (b) Retention of the 5 at. % film on STO(001) and Si(001) measured at 85 °C after being poled positively or negatively at 5 and 4.5 V, respectively. Red dashed lines are fits to $P_r = P_{0f_d}^{-n}$ (see ref 23). The vertical black dashed line marks a time of 10 years.

differences in the grain boundaries density or in grain boundaries microstructure.

The dielectric polarization loops of the films on STO(001) and Si(001) are shown in Figures 6a and 6b, respectively. There is almost no hysteresis in undoped films and 1 at. % La films, and it is small in 10 at. % La films. In contrast, hysteresis is evident in films with La concentration in the 2–7.5 at. %

range. The largest hysteresis is observed in 5 at. % La films, and 7.5 at. % films exhibit more pronounced hysteresis than films with 2 at. %. The permittivity loops of the samples with higher La concentration are more saturated due to lower coercive field. Therefore, hysteresis is more pronounced in films with lower La content showing higher ferroelectric polarization. There are also large differences in the dielectric constant values

of the films. Figure 6c shows the dependence of the permittivity at high voltage as a function of La concentration for films on STO(001) (red down triangles) and Si(001) (blue up triangles). The dielectric constant is higher in the films on Si(001), and it increases with La concentration on both substrates, from 21–27 in undoped and 1 at. % films to 30–35 in films with La concentration higher than 5 at. %. The homogeneity of the samples was confirmed by measuring different capacitors of the 2 and 7.5 at. % La samples (Supporting Information S10). The dielectric constants of HfO₂ polymorphs are reported to be around 24–29, 24–57, 36, and 19–25 for the orthorhombic, tetragonal, cubic, and monoclinic phases, respectively.^{39,40} The coexisting monoclinic phase (Figure 1a) in the undoped and lightly doped films explains the lower permittivity of these samples. Therefore, increasing La concentration results in the increase of the dielectric permittivity. Given that the cubic phase has the greatest dielectric permittivity, the dielectric permittivity increase with La content points to cubic phase formation in films with increasing La concentration, in agreement with observations on polycrystalline films.^{18,19} The crystalline phase evolution with the concentration of La, estimated from measurements of dielectric constant and XRD characterization, explains the dependence of P_r on the concentration of La (Figure 2). P_r is maximum in samples with 2–5 at. % La, being lower with lower and higher La content due to the greater amount of monoclinic and cubic paraelectric phases, respectively.

Figure 7a shows the endurance of the 2 and 5 at. % films on STO(001), which show the largest P_r , measured in both cases by applying bipolar pulses of 5 V amplitude. Wake-up is limited in both cases to fewer than ten cycles. After these few initial cycles both films suffer fatigue but no dielectric breakdown. The $2P_r = 24 \mu\text{C}/\text{cm}^2$ of the La 2 at. % film after 10 cycles decreases to $14.3 \mu\text{C}/\text{cm}^2$ after 10^6 cycles (41% polarization loss in 5 decades) and to 4.6 after 10^9 cycles (19% of the value after 10 cycles). In contrast, the 5 at. % film presents higher $2P_r = 31.5 \mu\text{C}/\text{cm}^2$ after 10 cycles and decreases slowly to $27.3 \mu\text{C}/\text{cm}^2$ after 10^6 cycles (13% polarization loss in 5 decades) and then more abruptly to $9.6 \mu\text{C}/\text{cm}^2$ after 10^9 cycles and to $5 \mu\text{C}/\text{cm}^2$ after 10^{10} cycles. Note that the larger P_r and superior endurance at 5 V cycling voltage of the 5 at. % film are a consequence of the lower coercive field, which allows for more saturated ferroelectric switching with a field low enough to avoid dielectric breakdown and important fatigue. Figure 7a includes also the endurance test of the samples of the same composition grown on Si. It can be observed that sample breakdown occurs at 10^8 and 10^9 (empty symbols) for 2% and 5% doping, respectively. The occurrence of sample breakdown is probably related to the higher leakage of samples grown on Si compared to those grown on STO. Interestingly, the endurance of the here reported epitaxial film is comparable to the best reported in the polycrystalline ones,¹⁸ in spite of the larger cycling voltage used here. This indicates that the lower defects amount in epitaxial films is crucial to allow electric cycling in harder conditions than in polycrystalline ones. Besides large endurance, applications require high retention of capacitors poled by using same electric field that in endurance measurements and for both polarities. The 5 at. % film, in addition of endurance above 10^{10} cycles, exhibits excellent retention at 85 °C (see retention measurements methodology in the Supporting Information S1), with extrapolated polarization beyond 10

years for both up and down polarization states after being poled at 5 V (Figure 7b). The retention measurement performed on the 5% sample grown on Si is also shown in Figure 7b, and similar good retention is observed at expenses of the mentioned P_r reduction. The same state (SS), new same state (NSS), and opposite state (OS) retention measurements at room temperature of the 5% sample grown on STO⁴¹ using different writing times have been performed. These are shown in Supporting Information S11. It can be observed that retention does depend on writing time pulse, indicating the presence of fluid imprint field.^{42,43}

4. CONCLUSIONS

In summary, epitaxial films of La-doped HfO₂ have been grown on LSMO buffered STO(001) and Si(001), and the impact of the La concentration on crystalline phases and electrical properties has been determined. There is large amount of monoclinic phase in lightly doped films, while the cubic phase appears in high La content films. All films show very smooth surfaces, confirming the potential usefulness of epitaxial films in devices based in ultrathin layers or in complex heterostructures. Films with 2–5 at. % La are mostly orthorhombic and have a high remanent polarization above $20 \mu\text{C}/\text{cm}^2$. The coercive field of the films on both substrates decreases with the concentration of La. The 5 at. % film on STO(001), which combines high polarization and a lower coercive field, has an endurance of 10^{10} cycles and negligible wake-up effect, with high extrapolated polarization after 10 years at 85 °C. The equivalent film on Si(001) has long retention also and slight wake-up effect, but leakage current is higher and the endurance is limited to 10^9 cycles.

■ ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acsaelm.1c00672>.

Retention measurements methodology; simulation of Laue oscillations; XRD θ – 2θ scans of the films on Si(001); topographic AFM images of films on STO(001); topographic AFM images of films on Si(001); PUND measurement of the films on STO(001); PUND measurement of the films on Si(001); piezoelectric force microscopy characterization; E_c dependence on thickness in polycrystalline and epitaxial films; dielectric loops measured in different capacitors; retention measurement with different pulse widths (PDF)

■ AUTHOR INFORMATION

Corresponding Authors

Ignasi Fina – Institut de Ciència de Materials de Barcelona (ICMAB-CSIC), 08193 Barcelona, Spain; orcid.org/0000-0003-4182-6194; Email: ifina@icmab.es

Florencio Sánchez – Institut de Ciència de Materials de Barcelona (ICMAB-CSIC), 08193 Barcelona, Spain; orcid.org/0000-0002-5314-453X; Email: fsanchez@icmab.es

Authors

Tingfeng Song – Institut de Ciència de Materials de Barcelona (ICMAB-CSIC), 08193 Barcelona, Spain

Huan Tan – Institut de Ciència de Materials de Barcelona (ICMAB-CSIC), 08193 Barcelona, Spain

Romain Bachelet – Univ. Lyon, Ecole Centrale de Lyon, INSA Lyon, CPE Lyon, CNRS, Institut des Nanotechnologies de Lyon - INL, UMR5270, Université Claude Bernard Lyon 1, 69134 Ecully, France; orcid.org/0000-0002-2910-0449

Guillaume Saint-Girons – Univ. Lyon, Ecole Centrale de Lyon, INSA Lyon, CPE Lyon, CNRS, Institut des Nanotechnologies de Lyon - INL, UMR5270, Université Claude Bernard Lyon 1, 69134 Ecully, France; orcid.org/0000-0002-3669-3406

Complete contact information is available at:
<https://pubs.acs.org/10.1021/acsaelm.1c00672>

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

Financial support from the Spanish Ministry of Science and Innovation, through the Severo Ochoa FUNFUTURE (CEX2019-000917-S), PID2020-112548RB-I00 (AEI/FEDER, EU), PID2019-107727RB-I00 (AEI/FEDER, EU), and MAT2017-85232-R (AEI/FEDER, EU) projects, from CSIC through the i-LINK (LINKA20338) program, and from Generalitat de Catalunya (2017 SGR 1377) is acknowledged. Project was supported by a 2020 Leonardo Grant for Researchers and Cultural Creators, BBVA Foundation. I.F. acknowledges Ramón y Cajal Contract RYC-2017-22531. T.S. and H.T. are financially supported by China Scholarship Council (CSC) with No. 201807000104 and 201906050014, respectively. T.S. and H.T.'s work has been done as a part of their Ph.D. program in Materials Science at Universitat Autònoma de Barcelona. R.B. and G.S.G. acknowledge the financial support from the European Commission through the project TIPS (No. H2020-ICT-02-2014-1-644453), from the French national research agency (ANR) through the projects DIAMWAFEL (No. ANR-15-CE08-0034), LILIT (No. ANR-16-CE24-0022), and MITO (No. ANR-17-CE05-0018), and from CNRS through the MITI interdisciplinary programs (project NOTE). They are also grateful to the joint laboratory INL-RIBER, P. Regreny, C. Botella, and J. B. Goure for the MBE technical support on the Nanolyon technological platform.

REFERENCES

- (1) Park, M. H.; Lee, Y. H.; Mikolajick, T.; Schroeder, U.; Hwang, C. S. Review and Perspective on Ferroelectric HfO₂-Based Thin Films for Memory Applications. *MRS Commun.* **2018**, *8* (3), 795–808.
- (2) Mikolajick, T.; Slesazek, S.; Park, M. H.; Schroeder, U. Ferroelectric Hafnium Oxide for Ferroelectric Random-Access Memories and Ferroelectric Field-Effect Transistors. *MRS Bull.* **2018**, *43* (5), 340–346.
- (3) Park, M. H.; Lee, Y. H.; Kim, H. J.; Kim, Y. J.; Moon, T.; Kim, K. Do; Müller, J.; Kersch, A.; Schroeder, U.; Mikolajick, T.; Hwang, C. S. Ferroelectricity and Antiferroelectricity of Doped Thin HfO₂-Based Films. *Adv. Mater.* **2015**, *27* (11), 1811–1831.
- (4) Kim, S. J.; Mohan, J.; Summerfelt, S. R.; Kim, J. Ferroelectric Hf_{0.5}Zr_{0.5}O₂ Thin Films: A Review of Recent Advances. *JOM* **2019**, *71* (1), 246–255.
- (5) Schröder, U.; Hwang, C. S.; Funakubo, H. *Ferroelectricity in Doped Hafnium Oxide: Materials, Properties and Devices*; Woodhead Publishing: 2019.
- (6) Park, M. H.; Lee, D. H.; Yang, K.; Park, J.-Y.; Yu, G. T.; Park, H. W.; Materano, M.; Mittmann, T.; Lomenzo, P. D.; Mikolajick, T.;

Schroeder, U.; Hwang, C. S. Review of Defect Chemistry in Fluorite-Structure Ferroelectrics for Future Electronic Devices. *J. Mater. Chem. C* **2020**, *8* (31), 10526–10550.

(7) Materano, M.; Lomenzo, P. D.; Kersch, A.; Park, M. H.; Mikolajick, T.; Schroeder, U. Interplay between Oxygen Defects and Dopants: Effect on Structure and Performance of HfO₂-Based Ferroelectrics. *Inorg. Chem. Front.* **2021**, *8* (10), 2650–2672.

(8) Fina, I.; Sánchez, F. Epitaxial Ferroelectric HfO₂ Films: Growth, Properties, and Devices. *ACS Appl. Electron. Mater.* **2021**, *3* (4), 1530–1549.

(9) Cao, J.; Shi, S.; Zhu, Y.; Chen, J. An Overview of Ferroelectric Hafnia and Epitaxial Growth. *Phys. Status Solidi RRL* **2021**, *15* (5), 2100025.

(10) Zhang, Z.; Hsu, S.; Stoica, V. A.; Paik, H.; Parsonnet, E.; Qualls, A.; Wang, J.; Xie, L.; Kumari, M.; Das, S.; Leng, Z.; McBriarty, M.; Proksch, R.; Gruverman, A.; Schlom, D. G.; Chen, L.; Salahuddin, S.; Martin, L. W.; Ramesh, R. Epitaxial Ferroelectric Hf_{0.5}Zr_{0.5}O₂ with Metallic Pyrochlore Oxide Electrodes. *Adv. Mater.* **2021**, *33* (10), 2006089.

(11) Song, T.; Tan, H.; Dix, N.; Moalla, R.; Lyu, J.; Saint-Girons, G.; Bachelet, R.; Sánchez, F.; Fina, I. Stabilization of the Ferroelectric Phase in Epitaxial Hf_{1-x}Zr_xO₂ Enabling Coexistence of Ferroelectric and Enhanced Piezoelectric Properties. *ACS Appl. Electron. Mater.* **2021**, *3* (5), 2106–2113.

(12) Wei, Y.; Nukala, P.; Salverda, M.; Matzen, S.; Zhao, H. J.; Momand, J.; Everhardt, A. S.; Agnus, G.; Blake, G. R.; Lecoer, P.; Kooi, B. J.; Íñiguez, J.; Dkhil, B.; Noheda, B. A Rhombohedral Ferroelectric Phase in Epitaxially Strained Hf_{0.5}Zr_{0.5}O₂ Thin Films. *Nat. Mater.* **2018**, *17* (12), 1095–1100.

(13) Yoong, H. Y.; Wu, H.; Zhao, J.; Wang, H.; Guo, R.; Xiao, J.; Zhang, B.; Yang, P.; Pennycook, S. J.; Deng, N.; Yan, X.; Chen, J. Epitaxial Ferroelectric Hf_{0.5}Zr_{0.5}O₂ Thin Films and Their Implementations in Memristors for Brain-Inspired Computing. *Adv. Funct. Mater.* **2018**, *28* (50), 1806037.

(14) Lyu, J.; Fina, I.; Solanas, R.; Fontcuberta, J.; Sánchez, F. Robust Ferroelectricity in Epitaxial Hf_{1/2}Zr_{1/2}O₂ Thin Films. *Appl. Phys. Lett.* **2018**, *113*, No. 082902.

(15) Shimizu, T.; Katayama, K.; Kiguchi, T.; Akama, A.; Konno, T. J.; Sakata, O.; Funakubo, H. The Demonstration of Significant Ferroelectricity in Epitaxial Y-Doped HfO₂ Film. *Sci. Rep.* **2016**, *6* (1), 32931.

(16) Müller, J.; Böske, T. S.; Schröder, U.; Mueller, S.; Bräuhäus, D.; Böttger, U.; Frey, L.; Mikolajick, T. Ferroelectricity in Simple Binary ZrO₂ and HfO₂. *Nano Lett.* **2012**, *12* (8), 4318–4323.

(17) Schenk, T.; Godard, N.; Mahjoub, A.; Girod, S.; Matavz, A.; Bobnar, V.; Defay, E.; Glinsek, S. Toward Thick Piezoelectric HfO₂-Based Films. *Phys. Status Solidi RRL* **2020**, *14* (3), 1900626.

(18) Chernikova, A. G.; Kuzmichev, D. S.; Negrov, D. V.; Kozodaev, M. G.; Polyakov, S. N.; Markeev, A. M. Ferroelectric Properties of Full Plasma-Enhanced ALD TiN/La: HfO₂/TiN Stacks. *Appl. Phys. Lett.* **2016**, *108*, 242905.

(19) Schroeder, U.; Richter, C.; Park, M. H.; Schenk, T.; Pešić, M.; Hoffmann, M.; Fengler, F. P. G.; Pohl, D.; Rellinghaus, B.; Zhou, C.; Chung, C. C.; Jones, J. L.; Mikolajick, T. Lanthanum-Doped Hafnium Oxide: A Robust Ferroelectric Material. *Inorg. Chem.* **2018**, *57* (5), 2752–2765.

(20) Mart, C.; Kühnel, K.; Kämpfe, T.; Zybelle, S.; Weinreich, W. Ferroelectric and Pyroelectric Properties of Polycrystalline La-Doped HfO₂ Thin Films. *Appl. Phys. Lett.* **2019**, *114*, 102903.

(21) Materlik, R.; Künneth, C.; Falkowski, M.; Mikolajick, T.; Kersch, A. Al-, Y-, and La-Doping Effects Favoring Intrinsic and Field Induced Ferroelectricity in HfO₂: A First Principles Study. *J. Appl. Phys.* **2018**, *123*, 164101.

(22) Li, X.; Li, C.; Xu, Z.; Li, Y.; Yang, Y.; Hu, H.; Jiang, Z.; Wang, J.; Ren, J.; Zheng, C.; Lu, C.; Wen, Z. Ferroelectric Properties and Polarization Fatigue of La: HfO₂ Thin-Film Capacitors. *Phys. Status Solidi RRL* **2021**, *15* (4), 2000481.

(23) Song, T.; Bachelet, R.; Saint-Girons, G.; Dix, N.; Fina, I.; Sánchez, F. Thickness Effect on the Ferroelectric Properties of La-

Doped HfO₂ Epitaxial Films down to 4.5 nm. *J. Mater. Chem. C* **2021**, *9* (36), 12224.

(24) Saint-Girons, G.; Bachelet, R.; Moalla, R.; Meunier, B.; Louahadj, L.; Canut, B.; Carretero-Genevri, A.; Gazquez, J.; Regreny, P.; Botella, C.; Penuelas, J.; Silly, M. G.; Sirotti, F.; Grenet, G. Epitaxy of SrTiO₃ on Silicon: The Knitting Machine Strategy. *Chem. Mater.* **2016**, *28* (15), 5347–5355.

(25) Lyu, J.; Fina, I.; Bachelet, R.; Saint-Girons, G.; Estandía, S.; Gázquez, J.; Fontcuberta, J.; Sánchez, F. Enhanced Ferroelectricity in Epitaxial Hf_{0.5}Zr_{0.5}O₂ Thin Films Integrated with Si(001) Using SrTiO₃ Templates. *Appl. Phys. Lett.* **2019**, *114*, 222901.

(26) Lyu, J.; Fina, I.; Fontcuberta, J.; Sánchez, F. Epitaxial Integration on Si(001) of Ferroelectric Hf_{0.5}Zr_{0.5}O₂ Capacitors with High Retention and Endurance. *ACS Appl. Mater. Interfaces* **2019**, *11* (6), 6224–6229.

(27) Lyu, J.; Song, T.; Fina, I.; Sánchez, F. High Polarization, Endurance and Retention in Sub-5 nm Hf_{0.5}Zr_{0.5}O₂ Films. *Nanoscale* **2020**, *12* (20), 11280–11287.

(28) Estandía, S.; Dix, N.; Chisholm, M. F.; Fina, I.; Sánchez, F. Domain-Matching Epitaxy of Ferroelectric Hf_{0.5}Zr_{0.5}O₂ (111) on La_{2/3}Sr_{1/3}MnO₃ (001). *Cryst. Growth Des.* **2020**, *20* (6), 3801–3806.

(29) Estandía, S.; Dix, N.; Gazquez, J.; Fina, I.; Lyu, J.; Chisholm, M. F.; Fontcuberta, J.; Sánchez, F. Engineering Ferroelectric Hf_{0.5}Zr_{0.5}O₂ Thin Films by Epitaxial Stress. *ACS Appl. Electron. Mater.* **2019**, *1* (8), 1449–1457.

(30) Kozodaev, M. G.; Chernikova, A. G.; Korostylev, E. V.; Park, M. H.; Schroeder, U.; Hwang, C. S.; Markeev, A. M. Ferroelectric Properties of Lightly Doped La: HfO₂ Thin Films Grown by Plasma-Assisted Atomic Layer Deposition. *Appl. Phys. Lett.* **2017**, *111*, 132903.

(31) Materano, M.; Lomenzo, P. D.; Mulaosmanovic, H.; Hoffmann, M.; Toriumi, A.; Mikolajick, T.; Schroeder, U. Polarization Switching in Thin Doped HfO₂ Ferroelectric Layers. *Appl. Phys. Lett.* **2020**, *117*, 262904.

(32) Fridkin, V. M.; Ducharme, S. General Features of the Intrinsic Ferroelectric Coercive Field. *Phys. Solid State* **2001**, *43* (7), 1320–1324.

(33) Lyu, J.; Fina, I.; Solanas, R.; Fontcuberta, J.; Sánchez, F. Growth Window of Ferroelectric Epitaxial Hf_{0.5}Zr_{0.5}O₂ Thin Films. *ACS Appl. Electron. Mater.* **2019**, *1* (2), 220–228.

(34) Pešić, M.; Fengler, F. P. G.; Larcher, L.; Padovani, A.; Schenk, T.; Grimley, E. D.; Sang, X.; LeBeau, J. M.; Slesazeck, S.; Schroeder, U.; Mikolajick, T. Physical Mechanisms behind the Field-Cycling Behavior of HfO₂-Based Ferroelectric Capacitors. *Adv. Funct. Mater.* **2016**, *26* (25), 4601–4612.

(35) Kozodaev, M. G.; Chernikova, A. G.; Korostylev, E. V.; Park, M. H.; Khakimov, R. R.; Hwang, C. S.; Markeev, A. M. Mitigating Wakeup Effect and Improving Endurance of Ferroelectric HfO₂ - ZrO₂ Thin Films by Careful La-Doping. *J. Appl. Phys.* **2019**, *125*, No. 034101.

(36) Song, T.; Bachelet, R.; Saint-Girons, G.; Solanas, R.; Fina, I.; Sánchez, F. Epitaxial Ferroelectric La-Doped Hf_{0.5}Zr_{0.5}O₂ Thin Films. *ACS Appl. Electron. Mater.* **2020**, *2* (10), 3221–3232.

(37) Sulzbach, M. C.; Estandía, S.; Long, X.; Lyu, J.; Dix, N.; Gázquez, J.; Chisholm, M. F.; Sánchez, F.; Fina, I.; Fontcuberta, J. Unraveling Ferroelectric Polarization and Ionic Contributions to Electroresistance in Epitaxial Hf_{0.5}Zr_{0.5}O₂ Tunnel Junctions. *Adv. Electron. Mater.* **2020**, *6* (1), 1900852.

(38) Lanza, M. A Review on Resistive Switching in High-k Dielectrics: A Nanoscale Point of View Using Conductive Atomic Force Microscope. *Materials* **2014**, *7* (3), 2155–2182.

(39) Materlik, R.; Künneth, C.; Kersch, A. The Origin of Ferroelectricity in Hf_{1-x}Zr_xO₂: A Computational Investigation and a Surface Energy Model. *J. Appl. Phys.* **2015**, *117*, 134109.

(40) Park, M. H.; Schenk, T.; Fancher, C. M.; Grimley, E. D.; Zhou, C.; Richter, C.; LeBeau, J. M.; Jones, J. L.; Mikolajick, T.; Schroeder, U. A Comprehensive Study on the Structural Evolution of HfO₂ Thin Films Doped with Various Dopants. *J. Mater. Chem. C* **2017**, *5* (19), 4677–4690.

(41) Mueller, S.; Muller, J.; Schroeder, U.; Mikolajick, T. Reliability Characteristics of Ferroelectric Si:HfO₂ Thin Films for Memory Applications. *IEEE Trans. Device Mater. Reliab.* **2013**, *13* (1), 93–97.

(42) Chernikova, A. G.; Markeev, A. M. Dynamic Imprint Recovery as an Origin of the Pulse Width Dependence of Retention in Hf_{0.5}Zr_{0.5}O₂-Based Capacitors. *Appl. Phys. Lett.* **2021**, *119*, No. 032904.

(43) Buragohain, P.; Erickson, A.; Kariuki, P.; Mittmann, T.; Richter, C.; Lomenzo, P. D.; Lu, H.; Schenk, T.; Mikolajick, T.; Schroeder, U.; Gruverman, A. Fluid Imprint and Inertial Switching in Ferroelectric La:HfO₂ Capacitors. *ACS Appl. Mater. Interfaces* **2019**, *11* (38), 35115–35121.

(44) Schenk, T.; Bencan, A.; Drazic, G.; Condurache, O.; Valle, N.; Adib, B. El; Aruchamy, N.; Granzow, T.; Defay, E.; Glinsek, S. Enhancement of Ferroelectricity and Orientation in Solution-Derived Hafnia Thin Films through Heterogeneous Grain Nucleation. *Appl. Phys. Lett.* **2021**, *118*, 162902.

(45) Quan, Z.; Wang, M.; Zhang, X.; Liu, H.; Zhang, W.; Xu, X. Excellent Ferroelectricity of 50 nm-Thick Doped HfO₂ Thin Films Induced by Annealing with a Rapid-Heating-Temperature Process. *AIP Adv.* **2020**, *10*, No. 085024.