



**HAL**  
open science

# Heteroepitaxial Growth of Lithium Niobate Thin Films on Sapphire Substrates with Different Orientations by Pulsed-Laser Deposition

Ihor Pershukov, Jérôme Richey, Emma Borel, Elisa Soulat, Marie Bousquet, Florian Dupont, Bertrand Vilquin

► **To cite this version:**

Ihor Pershukov, Jérôme Richey, Emma Borel, Elisa Soulat, Marie Bousquet, et al.. Heteroepitaxial Growth of Lithium Niobate Thin Films on Sapphire Substrates with Different Orientations by Pulsed-Laser Deposition. 2022 IEEE International Symposium on Applications of Ferroelectrics (ISAF 2022), IEEE, Jun 2022, Tours, France. 10.1109/ISAF51494.2022.9870044 . hal-03715485

**HAL Id: hal-03715485**

**<https://hal.science/hal-03715485>**

Submitted on 21 Mar 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Heteroepitaxial growth of Lithium Niobate Thin Films on sapphire substrates with different orientations by Pulsed-Laser Deposition

Ihor Pershukov<sup>1,2</sup>, Jérôme Richy<sup>1</sup>, Emma Borel<sup>1</sup>, Elisa Soulat<sup>1</sup>, Marie Bousquet<sup>1</sup>, Florian Dupont<sup>1</sup>, Bertrand Vilquin<sup>2</sup>

<sup>1</sup> Univ. Grenoble Alpes, CEA-LETI MINATEC-CAMPUS, 38000, France, [ihor.pershukov@cea.fr](mailto:ihor.pershukov@cea.fr);

<sup>2</sup> Univ Lyon, Ecole Centrale de Lyon, Université Claude Bernard Lyon 1, CPE Lyon, INSA Lyon, CNRS, INL UMR5270, 69130 Ecully, France

**Abstract**— In this study, epitaxial LiNbO<sub>3</sub> thin films were successfully grown on *a*- and *c*-Al<sub>2</sub>O<sub>3</sub> substrates by Pulsed Laser Deposition (PLD). In order to control the film crystallinity and chemical composition, the influence of different growth parameters, such as substrate temperature, oxygen pressure, and target composition, were studied. The physical and chemical properties of the as-deposited LiNbO<sub>3</sub> layers were characterized.

**Keywords** — pulsed laser deposition, ferroelectric thin film, lithium niobate, epitaxy.

## I. INTRODUCTION

With the deployment of the fifth generation of mobile communications (5G) and the Internet of Things, radiofrequency (RF) filters performances have to be improved. Nowadays, RF filters are mainly based on acoustic resonators such as Surface Acoustic Waves (SAW) and Bulk Acoustic Wave (BAW) resonators [1]. Thanks to their high electromechanical coupling coefficient (from 5.6% to 45.8% for bulk waves, depending on the crystalline orientation) and large acoustic velocity (from 3488 to 4750 m/s), single-crystal LiNbO<sub>3</sub> or LiTaO<sub>3</sub> layers are widely used in these applications [2].

LiNbO<sub>3</sub> is a piezoelectric material with a trigonal crystal structure (R3c space group), a Curie temperature around 1200 at near-stoichiometric compositions, low transmission loss, and high stability [3, 4].

Despite LiNbO<sub>3</sub> being known for more than 40 years, no growth technique has yet demonstrated layers with sufficient physical performances for practical use in optical or acoustic devices [4]. Indeed single-phased LiNbO<sub>3</sub> films are notoriously difficult to grow due to their lack of line composition, which makes the chemical composition control difficult. Li volatility is also an important factor to be taken into account. Another difficulty in the growth of this material lies in its high thermal expansion coefficient (TEC  $\alpha_a$  is 14.1  $10^{-6}$  (K<sup>-1</sup>) at 300 K) which can cause the presence of cracks [4]. As the natural growth orientation is along the *c*-axis, pure epitaxial growth along with specific directions (e.g. (1 1 0)) compatible with device specifications is also hard to be performed [2, 5]. Congruent composition of LiNbO<sub>3</sub> is nonstoichiometric (48.38 mol% of Li<sub>2</sub>O). The physical and structural properties of LiNbO<sub>3</sub> are dependent on the amount of Li in the film. For example, elastic constants, electromechanical coupling ( $k^2$ ), acoustic velocity, and refractive index, are highly dependent on the Li content of the film. So, for large-scale production of devices, it is necessary to precisely control the chemical composition [2, 6].

LiNbO<sub>3</sub> films are usually crystallized at substrate temperatures of 500-800°C [6, 7, 8]. Due to the high temperature of the deposition and high probability of growth mixes of LiNbO<sub>3</sub> with either Li<sub>3</sub>NbO<sub>4</sub> or LiNb<sub>3</sub>O<sub>8</sub> that represent centrosymmetric and hence non-ferroelectric phases, achieving the growth of stoichiometric LiNbO<sub>3</sub> thin films is challenging [4, 9].

In the litterature, lithium niobate films were grown epitaxially on *c*-Al<sub>2</sub>O<sub>3</sub> substrate using a thermal chemical vapor deposition method from the metalorganic compounds Li(C<sub>11</sub>H<sub>19</sub>O<sub>2</sub>) and Nb(OC<sub>2</sub>H<sub>5</sub>)<sub>5</sub>, in other words, by MOCVD[10]. Epitaxial LiNbO<sub>3</sub> thin (110) and (001) films were deposited on 10×10 mm<sup>2</sup> *a*-plane sapphire (Al<sub>2</sub>O<sub>3</sub>) and 12×7 mm<sup>2</sup> *c*-plane sapphire (Al<sub>2</sub>O<sub>3</sub>) substrates by Pulsed Laser Deposition (PLD) [11-12]. It was found that during the PLD process lower oxygen pressure (0.133 mbar) favors *a*-oriented LiNbO<sub>3</sub> film growth while higher oxygen pressure (0.667 mbar) favors *c*-oriented growth [13].

In this article, LiNbO<sub>3</sub> thin films have been deposited by Pulsed laser deposition (PLD) on *c*- and *a*-Al<sub>2</sub>O<sub>3</sub> substrates at 500 and 600°C. The atmosphere of oxygen (O<sub>2</sub>) with pressures of 0.007 and 0.2 mbar was used during the growth. In order to compensate a potential Li loss during PLD process, different targets were used: LiNbO<sub>3</sub> and LiNbO<sub>3</sub> with an additional 10% of Li<sub>2</sub>O. Dependences of the characteristics of the films on substrate orientation, pressure, temperature, and amount of Li in the target were studied.

This paper is organized as follows. The film growth process is described in Section II, and characterizations of the surface morphology and structural properties are shown in Section III. Finally, conclusions are presented in Section IV.

## II. EXPERIMENTAL PROCEDURE

The PLD system used in this study is a wafer-based PLD reactor made by Solmates. Laser ablation was done with a KrF excimer laser operating at 248 nm, with a repetition rate of 100 Hz and a laser fluence of 2.1 J/cm<sup>2</sup>. The target-substrate distance was 55 mm. Two targets with different compositions, namely a stoichiometric (LiNbO<sub>3</sub>) and a Li-enriched (10% of Li added to LiNbO<sub>3</sub>) were used to study the dependence of the films on the amount of Li atoms in the target. 4-inch *c*- and *a*-Al<sub>2</sub>O<sub>3</sub> wafers were chosen as substrates since their structure is compatible with LiNbO<sub>3</sub>. Two different oxygen pressures have been used in LiNbO<sub>3</sub> film deposition on *c*- and *a*-sapphire substrates, i.e., 0.2 mbar and 0.007 mbar. The deposition temperatures were 500°C and 600°C. Finally, combinations of deposition parameters are summarized in Table I.

TABLE I. DEPOSITION PARAMETERS USED FOR  $\text{LiNbO}_3$  GROWTH ON SAPPHIRE SUBSTRATES

Substrate orientation	Pressure (mbar)	Deposition temperature (°C)	Target
c- $\text{Al}_2\text{O}_3$	0.2	500	$\text{LiNbO}_3$
c- $\text{Al}_2\text{O}_3$	0.007	500	$\text{LiNbO}_3$
c- $\text{Al}_2\text{O}_3$	0.2	600	$\text{LiNbO}_3$
c- $\text{Al}_2\text{O}_3$	0.2	600	$\text{Li}_{1.1}\text{NbO}_{3.05}$
c- $\text{Al}_2\text{O}_3$	0.007	500	$\text{Li}_{1.1}\text{NbO}_{3.05}$
a- $\text{Al}_2\text{O}_3$	0.2	500	$\text{LiNbO}_3$
a- $\text{Al}_2\text{O}_3$	0.007	500	$\text{LiNbO}_3$
a- $\text{Al}_2\text{O}_3$	0.2	600	$\text{LiNbO}_3$
a- $\text{Al}_2\text{O}_3$	0.2	600	$\text{Li}_{1.1}\text{NbO}_{3.05}$
a- $\text{Al}_2\text{O}_3$	0.007	500	$\text{Li}_{1.1}\text{NbO}_{3.05}$

The growth rate of the films was about 11 nm/min and the film thicknesses are about 200 nm.

The surface morphology of  $\text{LiNbO}_3$  films was studied by both Scanning Electron Microscopy (SEM) and Atomic Force Microscopy (AFM). X-Ray Diffraction (XRD) in different configurations ( $\theta$ - $2\theta$  scan,  $\omega$  scan,  $\phi$  scan) was used to investigate the microstructural properties of the as-deposited  $\text{LiNbO}_3$  layers.

### III. RESULTS

#### A. $\text{LiNbO}_3$ films grown on c- $\text{Al}_2\text{O}_3$ substrate

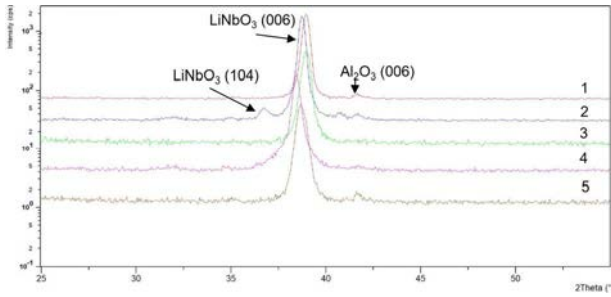


Fig. 1.  $\theta/2\theta$  XRD pattern of the  $\text{LiNbO}_3$  c-sapphire heterostructure grown at: (1) 0.2 mbar, 500°C,  $\text{LiNbO}_3$  target; (2) 0.007 mbar, 500°C,  $\text{LiNbO}_3$  target; (3) 0.2 mbar, 600°C,  $\text{LiNbO}_3$  target; (4) 0.2 mbar, 600°C,  $\text{Li}+\text{LiNbO}_3$  target; (5) 0.007 mbar, 500°C,  $\text{Li}+\text{LiNbO}_3$  target.

XRD patterns reveal that  $\text{LiNbO}_3$  films grown on c-sapphire show a strong (0 0 1) texture (Fig. 1). The film are single-phased and no parasitic phase (such as  $\text{Li}_3\text{NbO}_4$  and  $\text{LiNb}_3\text{O}_8$ ) was observed. The film grown at 500°C with the 0.007 mbar  $\text{O}_2$  pressure and  $\text{LiNbO}_3$  target is the only sample showing also (1 0 4) orientation, but still preferred texturation remains (0 0 6).

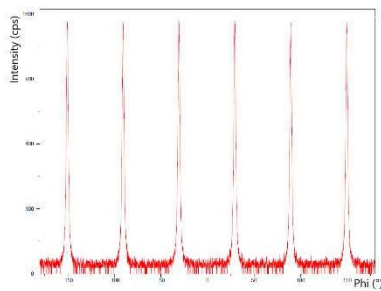


Fig. 2.  $\phi$ -scan  $\text{LiNbO}_3$  c-sapphire heterostructure grown at 0.2 mbar, 600°C,  $\text{LiNbO}_3$  target performed on  $\text{LiNbO}_3$  (0 0 6).

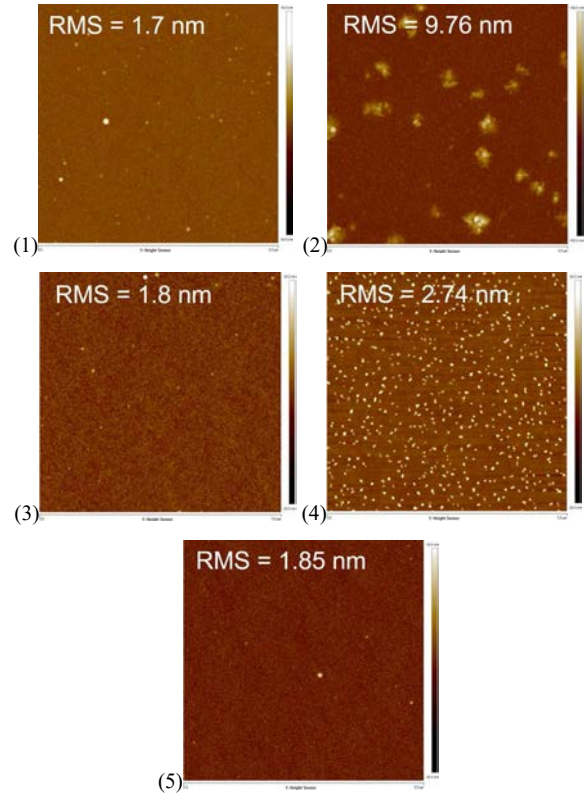


Fig. 3. AFM micrographs of  $\text{LiNbO}_3$  films deposited on c- $\text{Al}_2\text{O}_3$  substrates grown at different conditions: (1) 0.2 mbar, 500°C,  $\text{LiNbO}_3$  target; (2) 0.007 mbar, 500°C,  $\text{LiNbO}_3$  target; (3) 0.2 mbar, 600°C,  $\text{LiNbO}_3$  target; (4) 0.2 mbar, 600°C,  $\text{Li}+\text{LiNbO}_3$  target; (5) 0.007 mbar, 500°C,  $\text{Li}+\text{LiNbO}_3$  target. Scan size:  $(5 \times 5) \mu\text{m}^2$ .

Full Width at Half Maximum (FWHM) of  $\text{LiNbO}_3$  (0 0 6) peak obtained through symmetric  $\omega$ -scans is  $\sim 0.8^\circ$ , through asymmetric  $\omega$ -scans in between  $\sim 1.6$ - $2.1^\circ$  for (0 1 2). All  $\phi$ -scans (for example, Fig. 2) are having 6-fold symmetry confirming the epitaxial nature of all the samples.

The surface morphology of pulsed laser deposited  $\text{LiNbO}_3$  films was investigated by AFM measurements as shown in Fig. 3. Layers consisting of rounded grains can be seen whatever growth conditions. Little particles such as droplets are present in all cases.

As it is seen, the sample deposited at 0.007 mbar, 500°C, with  $\text{LiNbO}_3$  target has the highest root mean square (RMS) roughness, around 10 nm, which can be connected to coexistence of (001) and (104) orientations. For other samples surface of the layers is quite smooth with much lower roughness ( $\sim 2$  nm), but lower roughness ( $\sim 1$  nm) was already reported for z-cut of  $\text{LiNbO}_3$  [2]. SEM micrographs (Fig. 4.) confirm the low surface roughness of the films and the absence of the cracks.

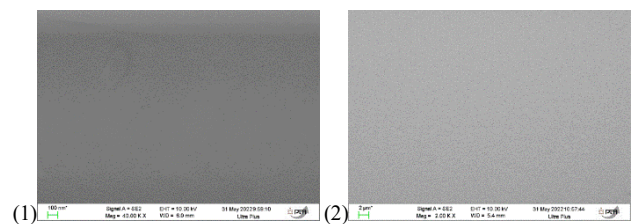


Fig. 4. SEM micrographs of  $\text{LiNbO}_3$  c- $\text{Al}_2\text{O}_3$  heterostructures grown at: (1) 0.2 mbar, 500°C,  $\text{LiNbO}_3$  target; (2) 0.2 mbar, 600°C,  $\text{LiNbO}_3$  target.

### B. $\text{LiNbO}_3$ films grown on $a\text{-Al}_2\text{O}_3$ substrate

Structural properties of the film were found to be greatly affected by the substrate orientation. Fig. 4 depicts the  $\theta/2\theta$ -XRD patterns from a  $\text{LiNbO}_3$  film when crystallization occurred during deposition on the  $a\text{-Al}_2\text{O}_3$  substrates. In contrast to what was previously observed for  $\text{LiNbO}_3$  films deposited on  $c\text{-Al}_2\text{O}_3$  (Fig. 4), a growth competition between (006) and (110) are systematically present (Fig. 5).

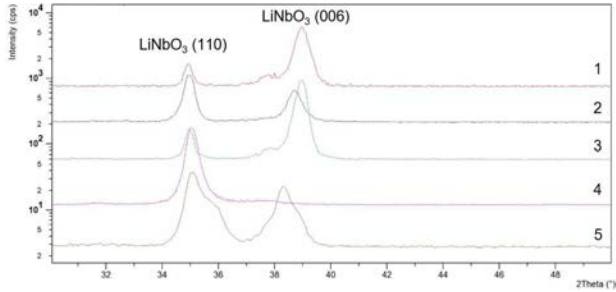


Fig. 5.  $\theta/2\theta$  XRD spectra of the  $\text{LiNbO}_3$   $a$ -sapphire heterostructure grown at: (1) 0.2 mbar, 500°C,  $\text{LiNbO}_3$  target; (2) 0.007 mbar, 500°C,  $\text{LiNbO}_3$  target; (3) 0.2 mbar, 600°C,  $\text{LiNbO}_3$  target; (4) 0.2 mbar, 600°C,  $\text{Li}+\text{LiNbO}_3$  target; (5) 0.007 mbar, 500°C,  $\text{Li}+\text{LiNbO}_3$  target.

XRD pattern reveals that  $\text{LiNbO}_3$  film deposited on  $a$ -sapphire at 600°C, under 0.2 mbar  $\text{O}_2$  atmosphere with the help of additional Li in the target is polycrystalline, with strong (1 1 0) texturation. Interesting is also the combination of both (0 0 6) and (1 1 0) orientations were grown on  $x$ -cut sapphire also with additional Li in the target, at 500°C with the 0.007 mbar  $\text{O}_2$  atmosphere. This indicates that nucleation at the point of solid-phase crystallization does not result in an ideal selection of the (1 1 0) orientation, although (1 1 0) is the major domain in the first growth stage, crystallization has selectivity to  $c$ -axis orientation.

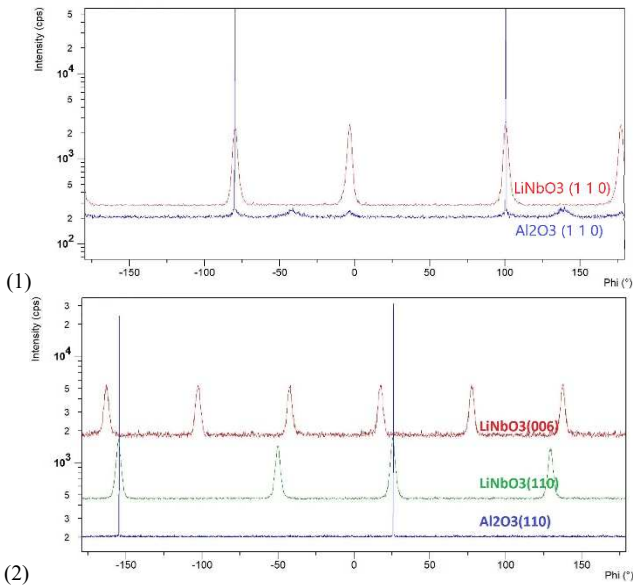


Fig. 6.  $\phi$ -scans of the  $\text{LiNbO}_3$   $a$ -sapphire heterostructures grown with  $\text{Li}+\text{LiNbO}_3$  target at: (1) 0.2 mbar, 600°C; (2) 0.007 mbar, 500°C.

All  $\phi$ -scans of samples grown with  $\text{LiNbO}_3$  target on the  $x$ -cut sapphire (not shown there) are having 6-fold symmetry confirming the epitaxial nature of the (0 0 1) layers. In Fig. 5  $\phi$ -scans of the  $\text{LiNbO}_3/c\text{-Al}_2\text{O}_3$  heterostructures grown with additional Li. The sample deposited at 600°C is having only (1 1 0)  $\text{LiNbO}_3$  grown. Heterostructure grown at low pressure with 10% of Li added to  $\text{LiNbO}_3$  target is having both epitaxial (0 0 1) and (1 1 0) oriented crystals in the film, which also confirms selectivity to  $c$ -axis orientation.

Full Width at Half Maximum (FWHM) of  $\text{LiNbO}_3$  (0 0 6) peaks grown with unenriched target obtained through symmetric  $\omega$ -scans are  $\sim 0.9^\circ$ - $1.7^\circ$ , through asymmetric  $\omega$ -scans in between  $\sim 2.0$ - $2.6^\circ$ . The same indicators of heterostructure grown at low pressure with 10% of Li added to the  $\text{LiNbO}_3$  target are  $\sim 1.2^\circ$  and  $\sim 2.2^\circ$ , respectively. Finally, for epitaxial  $\text{LiNbO}_3$  (1 1 0) grown at 600°C, FWHM obtained through symmetric and asymmetric  $\omega$ -scans are  $\sim 1.5^\circ$  and  $\sim 1.9^\circ$ , respectively.

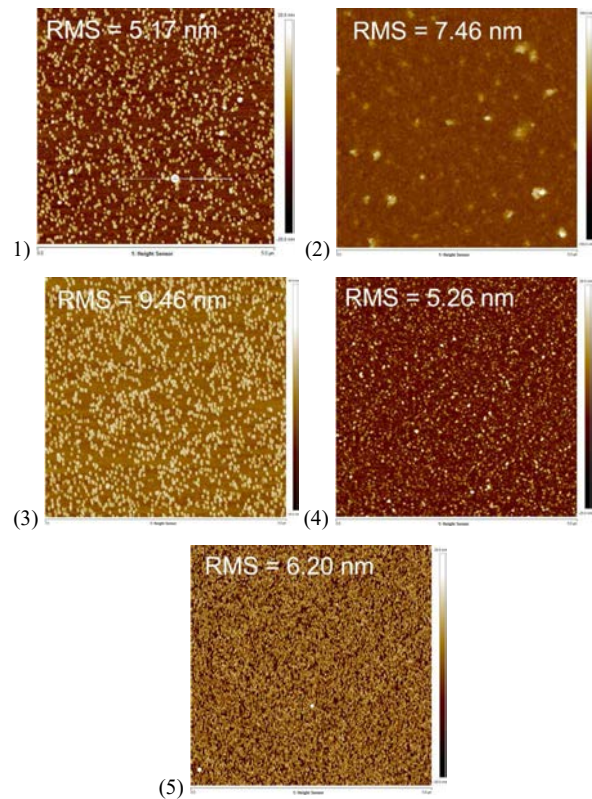


Fig. 7. AFM micrographs of  $\text{LiNbO}_3$  films deposited on  $a\text{-Al}_2\text{O}_3$  substrates grown at: (1) 0.2 mbar, 500°C,  $\text{LiNbO}_3$  target; (2) 0.007 mbar, 500°C,  $\text{LiNbO}_3$  target; (3) 0.2 mbar, 600°C,  $\text{LiNbO}_3$  target; (4) 0.2 mbar, 600°C,  $\text{Li}+\text{LiNbO}_3$  target; (5) 0.007 mbar, 500°C,  $\text{Li}+\text{LiNbO}_3$  target. Scan size:  $(5 \times 5) \mu\text{m}^2$ .

The surface morphology of  $\text{LiNbO}_3$  films grown on  $a\text{-Al}_2\text{O}_3$  substrate was also investigated with AFM measurements as shown in Fig. 6. Compared to lithium niobate grown on  $c\text{-Al}_2\text{O}_3$ , layers are also consisting of grains that can be seen in each sample but the number of particles on the surface is much bigger. Root mean square (RMS) roughness is also bigger in comparison to deposition on  $z$ -cut. Interestingly, the  $\text{LiNbO}_3$  film presenting the (1 1 0) epitaxial layer, *i.e.* film deposited at 600°C from a Li-enriched target, shows the least rough surface.

#### IV. CONCLUSIONS

In this work, LiNbO<sub>3</sub> thin films have been grown on 4-inch sapphire wafers in a wafer-based PLD reactor with film thicknesses of about 200 nm. The influence of different growth parameters, such as substrate orientation, temperature, oxygen pressure, and target composition, were studied. Single-phased films without parasitic phases (such as Li<sub>3</sub>NbO<sub>4</sub> and LiNb<sub>3</sub>O<sub>8</sub>) were observed.

Epitaxial, single-phase lithium niobate films with *c*-axis and *a*-axis orientations have been deposited and characterized. Predominant orientation toward the *c*-axis was shown. The conditions for LiNbO<sub>3</sub> film growth on *a*- and *c*-Al<sub>2</sub>O<sub>3</sub> substrates have been clarified. The *a*-axis orientation of LiNbO<sub>3</sub> thin film on *a*-Al<sub>2</sub>O<sub>3</sub> was achieved through the deposition with the help of an additional 10% of Li in the LiNbO<sub>3</sub> target and at 600°C substrate temperature. The possibility of growth of LiNbO<sub>3</sub>/Al<sub>2</sub>O<sub>3</sub> heterostructures with both epitaxial (0 0 1) and (1 1 0) oriented crystals in the film same time was shown. Future work will be devoted to the integration of the LiNbO<sub>3</sub>/Al<sub>2</sub>O<sub>3</sub> heterostructure in Surface Acoustic Wave device.

#### REFERENCES

- [1] R. Aigner, G. Fattinger, M. Schaefer, K. Karnati, R. Rothmund, and F. Dumont, "BAW Filters for 5G Bands," IEEE International Electron Devices Meeting (IEDM), 2018. doi: 10.1109/IEDM.2018.8614564.
- [2] A. Bartasyte, S. Margueron, T. Baron, S. Oliveri, and P. Boulet, "Toward High-Quality Epitaxial LiNbO<sub>3</sub> and LiTaO<sub>3</sub> Thin Films for Acoustic and Optical Applications," Adv. Mater. Interfaces, vol. 4, art. no. 1600998, 2017. doi: 10.1002/admi.201600998.
- [3] M. A. Mohammad, X. Chen, Q.-Y. Xie, B. Liu, J. Conway, H. Tian, Y. Yang, and T.-L. Ren, "Super High Frequency Lithium Niobate Surface Acoustic Wave Transducers up to 14 GHz," in IEEE International Electron Devices Meeting (IEDM), 2015. doi: 10.1109/IEDM.2015.7409729.
- [4] T. Volk and M. Wöhlecke, "Lithium Niobate: Defects, Photorefractive and Ferroelectric Switching"; Springer: Berlin/Heidelberg, Germany, 2008; Volume 115
- [5] B. Zivasatienraj, M.B. Tellekamp, and W.A. Doolittle, "Epitaxy of LiNbO<sub>3</sub>: Historical Challenges and Recent Success," Crystals, vol. 11, p. 397, 2021. doi: 10.3390/cryst11040397.
- [6] G. Balestrino *et al.*, "Epitaxial LiNbO<sub>3</sub> thin films grown by pulsed laser deposition for optical waveguides," Appl. Phys. Lett., vol. 78, pp. 1204–1206, 2001. doi: 10.1063/1.1350903.
- [7] A. K. Sarin Kumar *et al.*, "High-frequency surface acoustic wave device based on thin-film piezoelectric interdigital transducers," Appl. Phys. Lett., vol. 85, pp. 1757–1759, 2004. doi: 10.1063/1.1787897.
- [8] T.-H. Lee, F.-T. Hwang, C.-T. Lee, and H.-Y. Lee, "Investigation of LiNbO<sub>3</sub> Thin Films Grown on Si Substrate Using Magnetron Sputter," Mat. Sci. Eng. B, vol. 136, pp. 92-95, 2007. doi: 10.1016/j.mseb.2006.09.001.
- [9] S.-H. Lee, T. K. Song, T. W. Noh, and J.-H. Lee, "Low - temperature growth of epitaxial LiNbO<sub>3</sub> films on sapphire (0001) substrates using pulsed laser deposition," Appl. Phys. Lett., vol. 67, pp. 43-45, 1995, doi: 10.1063/1.115486.
- [10] Y. Akiyama, K. Shitanaka, H. Murakami, Y.-S. Shin, M. Yoshida, and N. Imaishi, "Epitaxial growth of lithium niobate film using metalorganic chemical vapor deposition," Thin Solid Films, vol. 515, pp. 4975–4979, 2007. doi: 10.1016/j.tsf.2006.10.034.
- [11] J. Y. Dai, H. K. Lam, Q. Li, J. Wang, H. L. W. Chan, and C. L. Choy, "Structural characterization and electron-energy-loss spectroscopic study of pulsed laser deposited LiNbO<sub>3</sub> films on a-sapphire," J. Appl. Phys., vol. 96, pp. 6319–6322, 2004. doi: 10.1063/1.1806993.
- [12] Y. Shibata, K. Kaya, K. Akashi, M. Kanai, T. Kawai, and S. Kawai, "Epitaxial growth and surface acoustic wave properties of lithium niobate films grown by pulsed laser deposition," J. Appl. Phys., vol. 77, pp. 1498–1503, 1995. doi: 10.1063/1.358900.
- [13] H. K. Lam, J. Y. Dai, and H. L. W. Chan, "Orientation controllable deposition of LiNbO<sub>3</sub> films on sapphire and diamond substrates for surface acoustic wave device application," J. Cryst. Growth, vol. 268, pp. 144–148, 2004. doi: 10.1016/j.jcrysgro.2004.04.111.