



HAL
open science

Alkali poisoning of Fe-Cu-ZSM-5 catalyst for the selective catalytic reduction of NO with NH₃

Houda Jouini, Imène Mejri, Joaquin Martinez-Ortigosa, Jose Cerillo, Carolina Petitto, Mourad Mhamdi, Teresa Blasco, Gérard Delahay

► To cite this version:

Houda Jouini, Imène Mejri, Joaquin Martinez-Ortigosa, Jose Cerillo, Carolina Petitto, et al.. Alkali poisoning of Fe-Cu-ZSM-5 catalyst for the selective catalytic reduction of NO with NH₃. *Research on Chemical Intermediates*, 2022, 48 (8), pp.3415-3428. 10.1007/s11164-022-04768-9 . hal-03755541

HAL Id: hal-03755541

<https://hal.science/hal-03755541>

Submitted on 22 Aug 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Alkali poisoning of Fe-Cu-ZSM-5 catalyst for the selective catalytic reduction of NO with NH₃

Houda Jouini^{1,2} · **Imène Mejri**^{1,2} · **Joaquin Martinez-Ortigosa**³ · **Jose L. Cerillo**³ · **Carolina Petitto**⁴ · **Mourad Mhamdi**^{1,2} · **Teresa Blasco**³ · **Gérard Delahay**⁴

¹ Université de Tunis El Manar, Faculté des Sciences de Tunis, LR01ES08 Laboratoire de Chimie des Matériaux et Catalyse, 2092, Tunis, Tunisie.

² Université de Tunis El Manar, Institut supérieur des technologies médicales de Tunis, 1006, Tunis, Tunisie.

³ Instituto de Tecnología Química, Universitat Politècnica de València - Consejo Superior de Investigaciones Científicas (UPV-CSIC), Avda. de los Naranjos s/n, 46022 Valencia, Spain.

⁴ ICGM, Université de Montpellier, CNRS, ENSCM, Montpellier, France.

Houda Jouini

+216 99 92 56 55

houda.jouini@fst.utm.tn

Abstract

Fe (2wt%)-Cu (1.5wt%)-ZSM-5 SCR catalyst was contacted 1.5 wt% of Na and 1.8 wt% of K in order to simulate poisoning by species more specifically contained in exhaust gases from exhaust gases of Diesel engines and power plants. Poisoning agents do not cause loss of surface area nor pore occlusion. XRD and SEM results showed that alkali metals introduction did not deteriorate the crystallinity and morphology of zeolite crystals. However, a significant loss of surface acidity was observed upon alkali-poisoned catalysts causing a dramatic deactivation of the NH₃-SCR of NO reaction. Na-doped catalyst showed higher low-

temperature SCR activity while potassium has a stronger deactivation effect on Fe-Cu-ZSM-5 than sodium beyond 400 °C.

Keywords Alkali metals; Deactivation; NH₃-SCR; NO; ZSM-5.

Introduction

Metal exchanged zeolite SCR catalysts, are among the most effective systems for nitrogen oxides (NO_x) abatement from exhaust gases of Diesel engines and power plants providing reduction of NO_x emissions up to 99% (Jouini et al. 2019; Jouini et al. 2018a, b). The durability of this category of catalysts dedicated to automotive applications regarding hydrothermal aging and chemical deactivation must be proven over the lifetime of the vehicle. These requirements are much more stringent than for stationary applications, since the catalysts are exposed to severe conditions: vibrations, high and varying exhaust temperatures, and deactivation by water and by different substances in the exhaust gas, which deposit on the catalyst surface (Chen et al. 2021; Ming et al. 2020; Xiong et al. 2020; Zhao et al. 2022).

Fuel and lubrication oil additives may contain significant amounts of alkali metals (Khodayari et al. 2001). Their deposition can significantly reduce the performances of the SCR catalysts since they may plug the pores of the catalyst channels and neutralize the Brönsted acid sites, thus decreasing the adsorption sites for ammonia, which play a crucial role in the NH₃-SCR mechanism (Wu et al. 2021).

Although several studies have been devoted to study the effect alkali metals on commercial vanadia-based catalysts (Feng et al. 2021; Köcher et al. 2008; Lisi et al. 2004; Peng et al. 2012; Zhou et al. 2020), the poisoning effect of alkali metals (Na and K) especially on zeolite based catalysts and mainly for the Fe-Cu-MFI system have seldom been reported. In this work, effect of addition of potassium or sodium and on the SCR activity of Fe-Cu-ZSM-5 catalyst was studied. Modifications of physico-chemical and catalytic properties occurring

upon poisoning have been investigated in order to define a correlation between the alteration of catalysts textures, metal speciation and acidity by alkali metals and their SCR activity.

Experimental

Catalyst preparation

Fe (2wt%)-Cu (1.5wt%)-ZSM-5 sample was prepared by consecutive solid-state ion exchange starting from commercial NH_4^+ -ZSM-5 (Si/Al=15) furnished by Zeolyst International (CBV3024E) as follow: 1 g of zeolite was mixed and finely ground with the desired amount of $\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$ in an agate mortar for 5 min under ambient conditions. The resulting mixture was then treated under a stream of helium (99.99%, Air Liquide, $30 \text{ cm}^3 \text{ min}^{-1}$) for 12 h at $380 \text{ }^\circ\text{C}$ ($2 \text{ }^\circ\text{C min}^{-1}$). The obtained powder was mixed and finely ground with the desired amount of $\text{FeCl}_2 \cdot 6\text{H}_2\text{O}$, then heated for 12 h at $290 \text{ }^\circ\text{C}$ in a stream of helium and under the same conditions described previously.

Catalyst poisoning

The alkali-poisoned samples were prepared by impregnating the aqueous solutions of NaCl (1.5 wt% Na) and KCl (1.8 wt% K) onto the fresh Fe-Cu-ZSM-5 catalyst powder for 4h under continuous stirring at ambient temperature. The obtained mixture was then dried overnight at 110°C . The prepared catalysts were denoted: Fe-Cu-Z, Na-Fe-Cu-Z and K-Fe-Cu-Z.

Activity measurements

The NH_3 -SCR of NO catalytic test was performed in temperature programmed surface reaction (TPSR) using a flow reactor operating at atmospheric pressure with a space velocity of $333,333 \text{ h}^{-1}$ and a total flow rate of 6 L h^{-1} . The concentrations of NH_3 and NO were established from initial gas cylinders containing 0.75% of NH_3/He and 0.75% of NO/He . 18 mg of each sample were activated in-situ at $250 \text{ }^\circ\text{C}$ under oxygen and helium mixture (8%

O₂/He) and then cooled to 200 °C. After reaching the starting reaction temperature, a by-pass of the reactor is done. From this step, the gas outlet composition was continuously monitored by vacuum stripping a fraction of the exit gas with a capillary towards the mass spectrometer (Pfeiffer Omnistar) equipped with Channeltron and Faraday detectors (0-200 amu) following the characteristic masses of: NH₃ (m/z =15, NH⁺), H₂O (m/z =18, H₂O⁺), N₂ (m/z = 28, N₂⁺), NO (m/z = 30, NO⁺) and N₂O (m/z = 44, N₂O⁺). Firstly, baselines of NH₃, N₂, NO and N₂O have been set under the mixture containing He, O₂ and water only (3.5% H₂O, 8% O₂ and 88.5% He). Then, the adequate flowrates of 0.75% NO/He and 0.75% NH₃/He were introduced and the He flowrate were adjusted in order to obtain the following gas composition: 1000 ppm of NO and 1000 ppm of NH₃. After attaining the stability of all characteristic mass lines, NO and NH₃ were introduced (mass flowmeters) and by adjusting the He flow, the reaction mixture is ready. Then, the by-pass is removed and the reaction mixture starts to pass through the catalyst. After 10 minutes of dwell, the temperature was increased from 200 °C to 550 °C. The catalytic results were expressed as follows:

Conversion of the reactant R (R=NO or NH₃):

$$X_R = \frac{[R_0] - [R_T]}{[R_0]} \times 100, \text{ where } [R_0] \text{ and } [R_T] \text{ are the concentrations of the reactant R at the inlet gas}$$

reactor and at the temperature T, respectively.

Amount of N₂O formed:

$$Q_{N_2O} = [N_2O|T] - \frac{[N_2O|inj]}{[N_2O|0] - [N_2O|inj]} \times 1000, \text{ where } [N_2O_{inj}] \text{ is the concentration of N}_2\text{O}$$

before injection, [N₂O_T] and [N₂O₀] represent the concentrations of N₂O at the temperature T and at the inlet gas reactor, respectively.

Selectivity toward N₂:

$$S_{N_2} = \frac{[(X_{NO} \times 1000) + (X_{NH_3} \times 1000)] - Q_{N_2O}}{(X_{NO} \times 1000) + (X_{NH_3} \times 1000)} \times 100$$

Catalyst characterization

The chemical analysis of the studied materials was carried out by ICP-AES in a Varian 715-ES spectrometer. The powder samples (ca 20-30 mg) were dissolved in an acid mixture of 20% HNO₃: 20% HF: 60% HCl (% vol) and aged during 24 h. The calibration curve was fitted to the predicted approximate concentration of analyse and determined using standard solutions (Sigma-Aldrich). The wavelengths used for Cu and Fe analysis were 327.395 and 234.350 nm, respectively. N₂ physisorption measurements were determined with an automatic ASAP 2020 apparatus from Micromeritics. Before the nitrogen adsorption, the samples were outgassed at 250 °C until a static vacuum of 3×10⁻⁵ bar was reached. BET model was used to calculate the specific surface areas, while pore volumes were calculated at the end of the step corresponding to the filling of the pores (at P/P^o=0.98). STEM observations were performed using a JEOL-JEM 2100F instrument equipped with an X-MAX microanalysis detector and operating under an accelerating voltage of 200 kV and a resolution energy of 20 eV. The morphology of samples was observed by FE-SEM on a ZEISS AURIGA 55 Compact instrument in combination with an EDX detector. The sample powder was deposited in double-sided tape and analysed without metal covering. The samples crystallinity was checked using a PANalytical Cubix'Pro diffractometer equipped with an X'Celerator detector using Cu-Kα radiation (0.154056 nm). The equipment is working under a voltage of 45 kV and a current of 40 mA. The diffractograms were recorded in the region of 5-40° and were exploited with the software PANalytical X'Pert HighScore Plus. The phase identification was accomplished by comparing the experimental diffractograms with the references of the

international database ICDD (The International Centre for Diffraction Data). XPS analyses were performed using a SPECS spectrometer equipped with a MCD-9 detector. The source is composed of an aluminium anode emitting a monochromatic X-ray radiation ($K\alpha = 1486.6$ eV). NH_3 -TPD profiles were obtained on an automated Micromeritics Autochem II analyser. Before NH_3 -TPD measurements, samples (50 mg) were pre-treated in a quartz U-tube reactor under air flow ($10 \text{ cm}^3 \text{ min}^{-1}$) at $500 \text{ }^\circ\text{C}$ ($10 \text{ }^\circ\text{C min}^{-1}$) for 1 hour and then cooled under helium ($100 \text{ cm}^3 \text{ min}^{-1}$) to $100 \text{ }^\circ\text{C}$. The ammonia was adsorbed ($10 \text{ cm}^3 \text{ min}^{-1}$) during 1 hour then adsorbed under helium atmosphere ($100 \text{ cm}^3 \text{ min}^{-1}$) to $800 \text{ }^\circ\text{C}$ ($10 \text{ }^\circ\text{C min}^{-1}$). DRS UV-vis measurements were performed on a Perkin Elmer Lambda 45 spectrophotometer equipped with a diffuse reflectance attachment. Spectra were recorded at room temperature in the wavelength range of 200-900 nm using BaSO_4 as reference material.

Results and discussion

Physico-chemical characterisation

The chemical analysis was performed by ICP-AES technique. Obtained results are gathered in Table 1 including Fe, Cu, Na and K contents. Examination of ICP results shows that metals are well retained by the zeolite during the preparation process where the experimental amounts approximate the theoretical values set for the catalysts preparation.

Table 1ICP-AES chemical analysis and N₂ physisorption at 77 K results.

Sample	Fe (wt%)	Cu (wt%)	Na/K (wt%)	S _{BET} ^a (m ² /g)	Pore volume ^b (cm ³ /g)	Micropore volume ^c (cm ³ /g)
NH ₄ ⁺ -ZSM-5	-	-	-	336	0.15	0.12
Fe-Cu-Z	1.83	1.40	-	327	0.13	0.11
Na-Fe-Cu-Z	1.79	1.22	1.42	311	0.17	0.12
K-Fe-Cu-Z	1.79	1.24	1.79	347	0.14	0.10

^acalculated by BET method, ^bcalculated by BJH method, ^ccalculated by t-plot method

XRD patterns of unpoisoned catalyst show the typical signals of parent zeolite as shown in Figure 1. No signals attributable to the Fe and/or Cu oxide aggregates suggesting a good dispersion of the active phases. The principal diffraction peaks intensities of the parent zeolite decreased with metals addition due to the higher absorption coefficient of copper and iron compounds for the X-ray radiation (Qi et al. 2005).

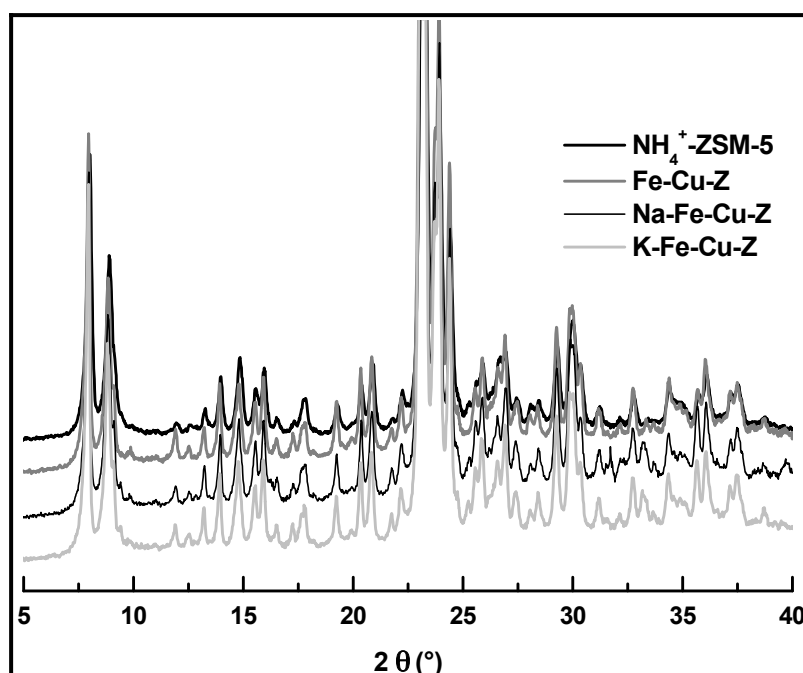


Fig. 1 XRD diffractograms of prepared catalysts.

XRD patterns of poisoned samples are superimposable to those of the corresponding pure catalyst suggesting that no detectable formation of alkaline metal oxides occurs. A negligible effect of poisoning agents on the surface area of the samples was also observed (Table 1). The S_{BET} of K-poisoned sample was slightly improved suggesting a partial modification of the external surface of the catalyst. Pore size distribution confirms that no significant pore blocking occurs upon poisoning.

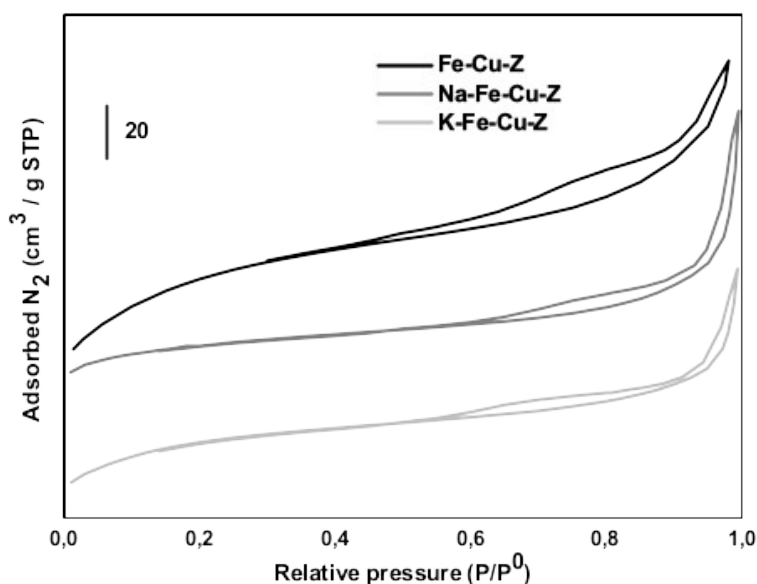


Fig. 2 N₂ Adsorption-desorption isotherms of prepared catalysts.

The porosity of zeolite nanoparticles before and after poisoning treatment was investigated by N₂ sorption analysis (Fig.2). The shapes of nitrogen adsorption-desorption isotherms showed the typical Type H3 loop in the case of fresh sample while alkali poisoned samples showed the Type H4 loop according to the classification of IUPAC indicating the presence of mesoporosity formed by the packing of zeolite nanocrystals (Beznis et al. 2010). The hysteresis loop of the fresh sample are larger than those of poisoned samples, suggesting that poisoning treatment affects the pore shapes of the ZSM-5.

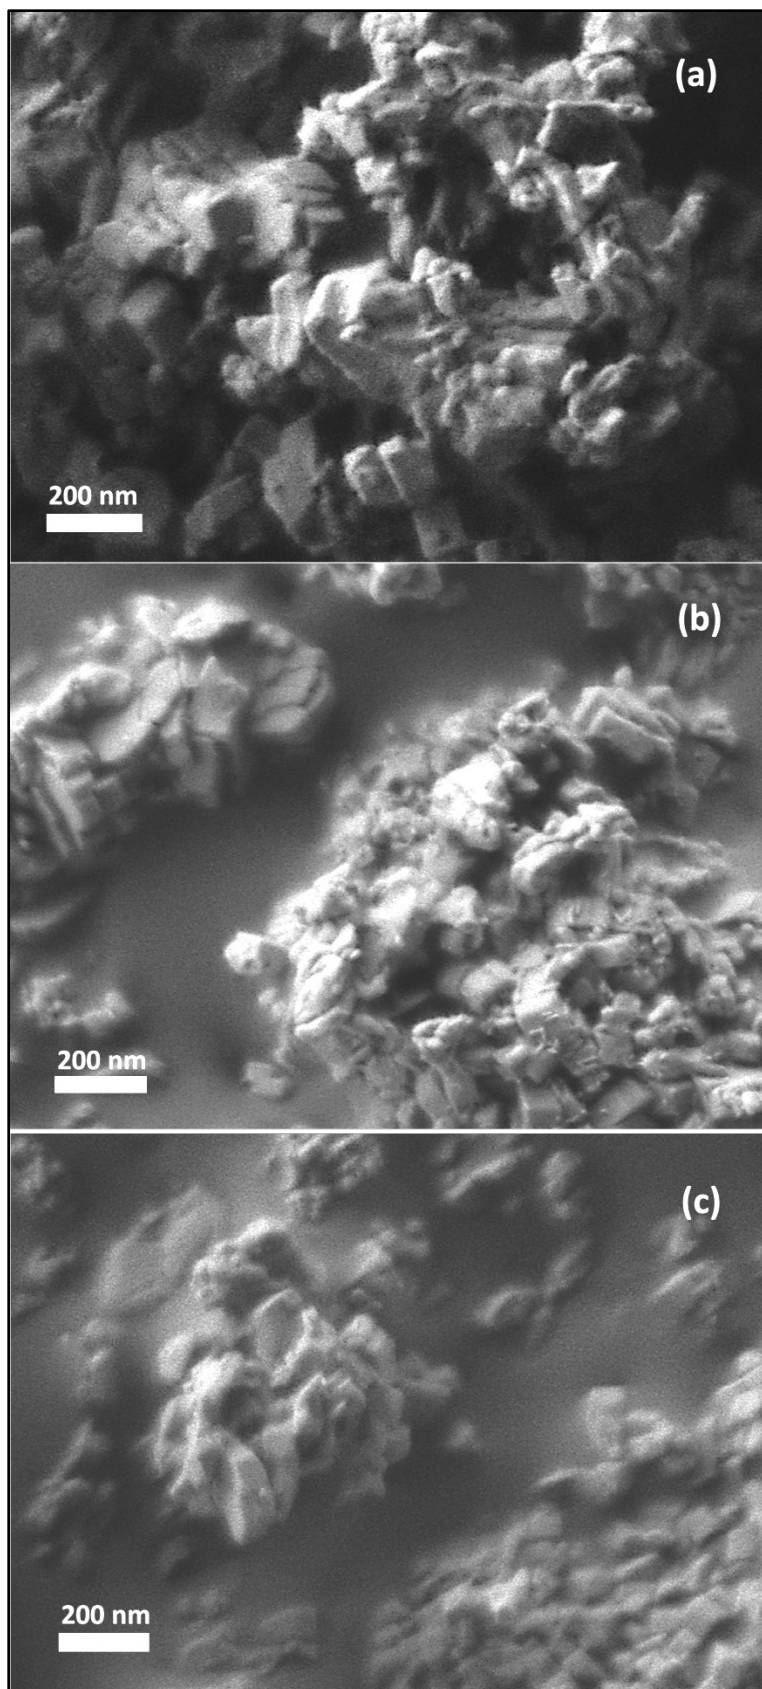


Fig. 3 SEM micrographs in the magnitude 50000x of Fe-Cu-Z (a), K-Fe-Cu-Z (b) and Na-Fe-Cu-Z (c).

SEM/EDX analysis was performed on the studied catalysts and the obtained micrographs were presented in Figure 3 showing that the morphology was not modified by poisoning as concerns both shape and dimension of catalyst particles.

Figure 4 shows STEM micrographs of the catalysts. The distribution of copper and iron species were studied by EDX elemental analysis showing that nano-sized metal species (<100 nm) were formed. The size of the particles indicate that they are located on the outer surface of the zeolite (Beznis et al. 2010). STEM image of Fe-Cu-Z (Fig. 4a), showed highly dispersed iron particles (spectra 25, 26 and 27) with a size of 8-20 nm. They coexist with smaller Fe-Cu nanocomposites (spectrum 22) as confirmed by EDX analysis with an average size of 3 nm. In the case of Na-Fe-Cu-Z (Fig. 4b), larger iron oxide particles (30-60 nm) are observed (spectra 26 and 29) together with large copper oxide particles (40 nm) and Fe-Cu nanocomposites (spectra 27 and 28) of about 12 nm. EDX analysis showed that metal species are rather agglomerated compared to the fresh sample. The STEM micrograph of K-Fe-Cu-Z (Fig. 4c) showed differently sized iron oxide particles (8-88 nm) with a rather uniform distribution. A limited number of Fe-Cu nanocomposites was detected for this catalysts with an average size of 8 nm (spectrum 22).

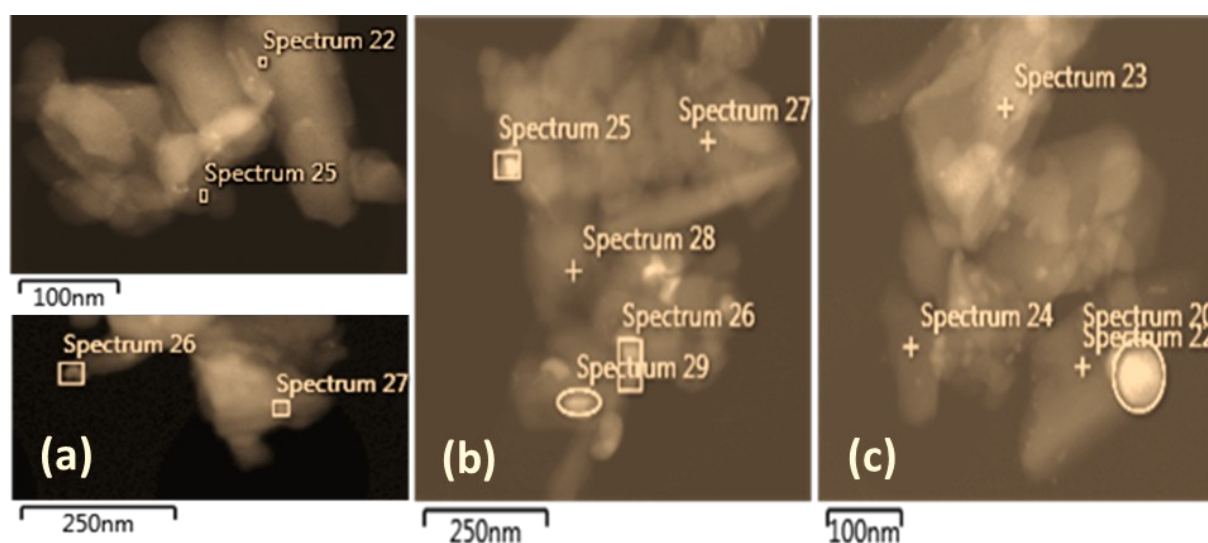


Fig. 4 STEM micrographs of Fe-Cu-Z (a), K-Fe-Cu-Z (b) and Na-Fe-Cu-Z (c).

It can be concluded that sodium deposition promotes the aggregation of copper species while potassium deposition promotes the aggregation of iron particles. In addition, while potassium is uniformly distributed, sodium is more concentrated on the catalysts particles.

Table 2

EDX elemental analysis results

Sample	Spectrum	Element (wt%)						
		O	Al	Si	Cl	Fe	Cu	Na/K
	22	47.73	1.55	40.31	0.40	1.60	8.41	-
Fe-Cu-Z	25	54.85	0	26.32	0.33	18.50	0	-
	26	46.15	0	12.44	0.18	41.22	0	-
	27	51.87	1.95	33.41	1.18	11.59	0	-
	25	16.15	0	10.22	11.69	0	61.53	0.41
Na-Fe-Cu-Z	26	46.72	1.29	21.03	0.26	30.40	0.04	0.26
	27	52.70	2.05	42.89	0.06	0.24	1.29	0.14
	28	47.78	0	49.57	0.07	0.29	2.29	0
	29	46.09	1.19	28.85	0.10	23.21	0.02	0.54
	20	46.71	0.93	17.32	0	34.15	0	0.88
K-Fe-Cu-Z	22	52.01	0	1.43	0.16	0.23	0	0.22
	23	52.12	0	47.32	0	0	0	0.57
	24	39.61	0	39.04	0.2	17.61	0	3.55

The valence and coordination state of Fe and Cu species present in the prepared catalysts were determined by UV-vis spectroscopy. The Kubelka-Munk function was calculated from reflectance measurements and the recorded spectra were shown in Figure 5.

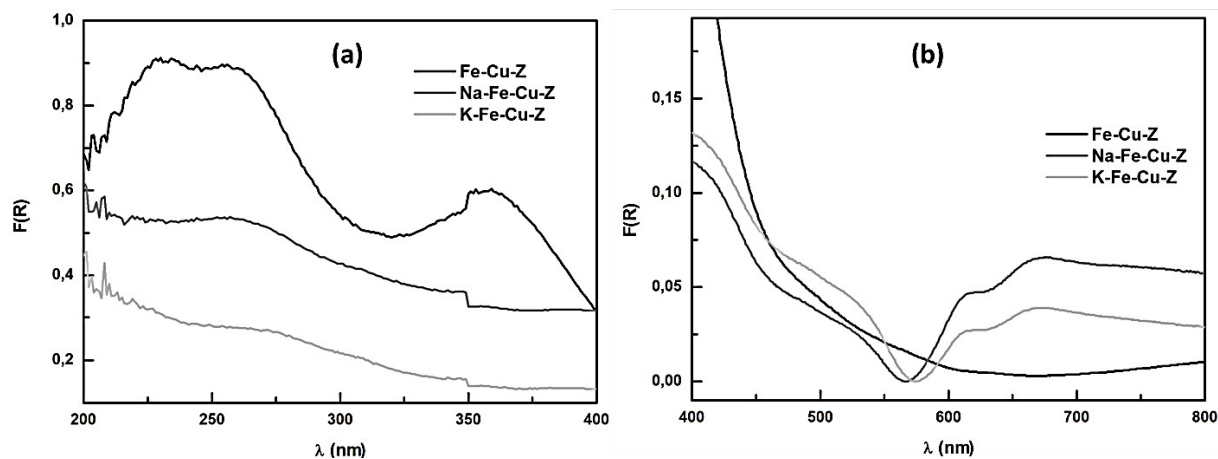


Fig. 5 DRS UV-vis spectra of studied catalysts

UV-vis spectrum of the unpoisoned catalysts showed two absorption bands at around 232 and 256 nm: the first is a d-d charge transfer band assigned to Fe^{3+} species in tetrahedral coordination ($e \rightarrow t_2$) (Pérez-Ramírez et al. 2005), while the second originates mainly from the p-d charge transfer transition between framework oxygen and Fe^{3+} cations (Sun et al. 2008). Oligonuclear $\text{Fe}^{3+}_x\text{O}_y$ clusters are characterized by bands located in the range of 300-400 nm (Bordiga et al. 1996), thus the band appearing at 357 nm was assigned to $\text{Fe}^{3+}_x\text{O}_y$ clusters

Na and K-poisoned samples showed the same UV-vis profile: the p-d charge transfer transition between framework oxygen and Fe^{3+} and the signal of oligonuclear $\text{Fe}^{3+}_x\text{O}_y$ clusters were both detected with a slight bathochromic shift compared to Fe-Cu-Z sample probably due to the difference in the environment of metallic species after the poisoning treatment.

Additional broad bands located at $\lambda > 600$ nm attributable to $t_{2g} \rightarrow e_g$ transitions of Cu^{2+} ions in octahedral symmetry were detected for both poisoned samples only (Chanquía et al. 2010).

Temperature programmed desorption of NH_3 (NH_3 -TPD) experiments were carried out on the pure catalyst and poisoned samples to determine the amount and strength of their different acid sites. The desorption temperatures determined from the NH_3 -TPD analysis and the corresponding amounts of ammonia consumption evaluated from the integration of TPD curves are presented in Table 3.

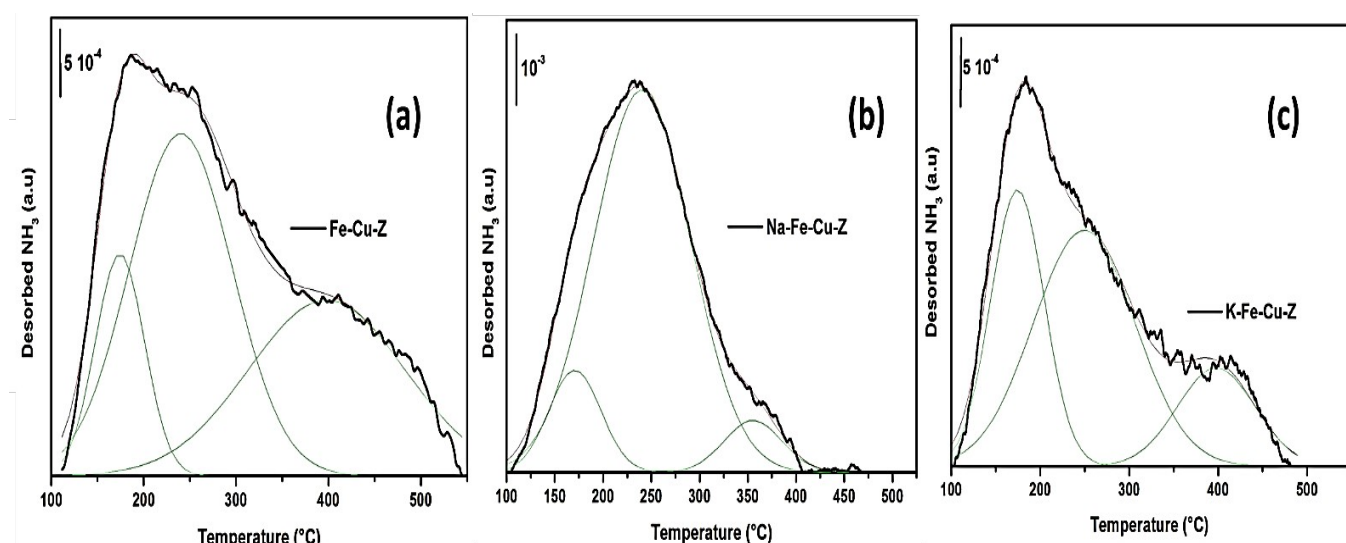


Fig. 6 NH_3 -TPD profiles of Fe-Cu-Z (a), K-Fe-Cu-Z (b) and Na-Fe-Cu-Z (c).

Figure 6(a) shows the NH₃-TPD profiles of Fe-Cu-Z. The fresh catalyst exhibits a low temperature peak (peak-l) corresponding to the desorption of weakly chemisorbed ammonia on Lewis and/or weak Brønsted acid sites, or silanol groups (Jouini et al. 2018a). The high temperature peak (peak-h) is assigned to the desorption of strongly chemisorbed ammonia on strong Brønsted acid sites (Si-OH⁺-Al) (Jouini et al. 2018a). The desorption peak located at intermediate temperature (peak-i) is attributed to ammonia desorption from medium-strength acid sites. The deposition of alkali metals substantially reduces surface acidity mainly affecting strong acid sites, which are eliminated of about 85.7 and 74.3 % for Na-Fe-Cu-Z and K-Fe-Cu-Z samplers respectively. The effect of potassium is more pronounced compared to that of sodium on the base of the same molar concentration as it can be noticed from the quantitative study reported in Table 3. K⁺ ions easily diffuse into the pore channels of the zeolite (Liu et al. 2020). They can thus dislodge and replace protons and metal ions (Cu or Fe) and therefore induce a consequent decrease in Brønsted acid sites and Lewis sites, respectively (Lisi et al. 2020).

This stronger effect of potassium compared to sodium was also observed by Zhu et al in the NH₃-SCR of NO_x over Cu-SSZ-39 (Zhu et al. 2020). Fan et al., to explain this, proposed that the smaller diameter of hydrated potassium and its higher binding capacity makes its diffusivity much stronger than that of sodium (Fan et al. 2018). This finding is in agreement with the higher deactivation effect of potassium observed in our NH₃-SCR catalytic tests.

The obtained results indicate that the amount of NH₃ adsorption is the major difference between the fresh and poisoned catalysts, which is responsible for the reaction activity. As reported in the literature, alkali metals atoms can directly dislodge the active catalyst sites from exchange sites of the catalyst (Zhang et al. 2021), thus lower the surface acidity by prohibiting ammonia adsorption (Peng et al. 2012), and change the nature of copper sites.

Table 3NH₃-TPD quantitative study.

Sample	Acidity ^a			Total	Loss in strong acid sites (%)
	“l” peak	“i” peak	“h” peak		
Fe-Cu-Z	0.14 (174)	0.45 (240)	0.35 (398)	0.94	-
Na-Fe-Cu-Z	0.08 (171)	0.59 (240)	0.05 (355)	0.72	85.71
K-Fe-Cu-Z	0.18 (174)	0.29 (249)	0.09(398)	0.56	74.28

^a Expressed in mmol of NH₃/g of sample, ^b Temperature of maximum desorption of low (l), intermediate (i) and high (h) peaks expressed in °C

NH₃-SCR catalytic activity

In Figure 7, results of catalytic tests, expressed in conversion of NO as function of temperature, are reported for unpoisoned and alkali poisoned catalysts. The fresh catalyst achieved above 90 % of NO conversion at 350-500 °C and a weak amount of N₂O was detected for this catalyst compared to the poisoned ones as shown in Figure 8. The NO/NH₃ conversion ratio was close to 1 for the fresh catalyst in the temperature window 425-485 °C and then the conversion of NO slightly decreased of about 5%. A second test on the same aliquot led to the same NO conversion profile (not shown), thus showing the stability of the catalyst and also validating the TPSR method for measuring the NO conversion.

After the addition of alkali metals, both poisoned catalysts were severely deactivated within the whole testing temperature range. The catalyst containing sodium has a better low-temperature SCR activity than that containing potassium. The highest conversion of NO recorded for Na-Cu-Fe-Z was about 93 % around 400 °C. Then this NO conversion first decreases slowly on a window of 50 °C above this temperature and after decreases rapidly to reach 52% at 550 °C, due to strong ammonia oxidation activity. Therefore this NO conversion profile is a volcano-type curve which can be attributed, according to previous studies (Mehsein et al. 2019, Tarot et al. 2019) to copper oxide sintering.

The catalytic profile of the K-doped catalyst exhibits, with respect to Fe-Cu-Z, a loss of conversion into NO of 30-35 % at low temperature, loss which diminishes with the increase of temperature. A maximum of conversion slightly inferior at 90 %. is reached at 470 °C. Above this latter temperature, a weak NO conversion decrease is observed. This conversion decrease follows the same trend as that of the fresh catalyst. Therefore K-Fe-Cu-Z behaves differently than Na-Fe-Cu-Z. The higher loss of activity, at low temperatures, of K-Fe-Cu-Z can be attributed to the stronger aggregation of iron species, observed before for this catalyst (STEM and EDX analyses). On the other hand, the quite stability of the NO reduction activity at temperature above 470°C could be attributed to the better maintain of the copper species at the exchange sites.

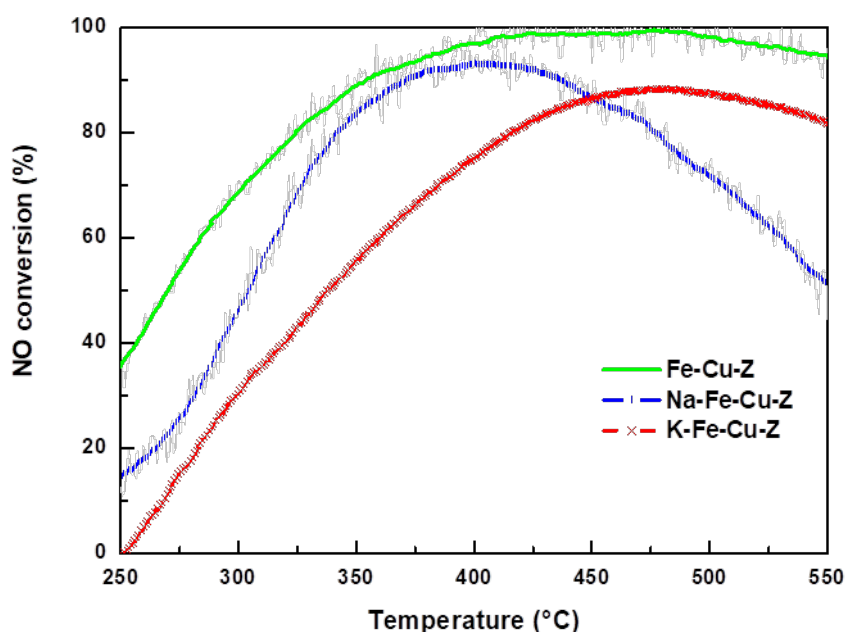


Fig.7 NO conversion over the prepared catalysts.

A good correlation is observed between the SCR activity and the evolution of N_2O^+ fragment intensity. The Na-poisoned catalysts showed severely worsened high-temperature activity for NO conversion compared to K-Cu-Fe-Z, which was due to an important NH_3 oxidation ($4 NH_3 + 5 O_2 \rightarrow 4 NO + 6 H_2O$). As regards to the side reactions, the catalysts have tendency to

form nitrous oxide ($4 \text{ NH}_3 + 4 \text{ NO} + 3 \text{ O}_2 \rightarrow 4 \text{ N}_2\text{O} + 6 \text{ H}_2\text{O}$) at high temperature ($> 400 \text{ }^\circ\text{C}$) instead of decomposing NO in the presence of NH_3 as a reducing agent (Madia et al. 2002).

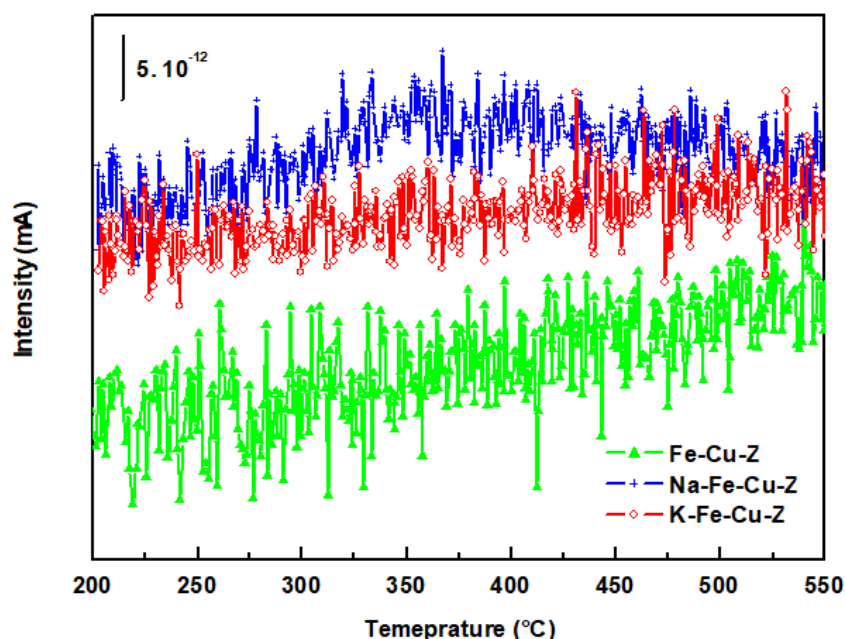


Fig. 8 Evolution of N_2O^+ fragment ($m/e=44$) intensity over the prepared catalysts.

Discussion

Deposition of small amount of alkaline metals (1.5 wt% of Na and 1.8%wt of K) leads to a dramatic deterioration of catalytic activity and a significant loss of surface acidity compared to fresh Fe-Cu-Z sample. At the same molar concentration of alkali metals, potassium gives rise to a more significant deactivation effect with regard to sodium at the low temperature range, related to its better neutralising properties of acid sites. Strong acid centres adsorbing NH_3 at temperature above $350 \text{ }^\circ\text{C}$, which are not involved in the SCR mechanism occurring at lower temperatures, are more neutralised by sodium while the neutralizing effect of potassium affects more medium and weak acid sites leading to a lower catalytic activity compared to the catalyst doped with sodium (Lisi et al. 2004). The STEM-EDX study revealed the highest aggregation degree of Na-Fe-Cu-Z. Observations on different regions of the sample showed the presence of large iron and copper oxides which may explain the deterioration of the

catalyst at high reaction temperature. In fact, the side reaction of ammonia oxidation reaction is promoted by the presence of large metal oxide particles, mainly CuO which was detected only for the Na doped catalyst (Sjövall et al. 2006). This explains the higher loss of NO conversion observed for Na-Fe-Cu-Z at temperature above 450°C.

Neither significant structural and textural changes were detected for our catalysts, indicating that deactivation was caused only by changes in the distribution and coordination of iron and/or copper species and mainly on the acidic properties of the catalysts, in agreement with previous reports (Tarot et al. 2019; Wu et al. 2022).

Conclusion

Fe-Cu-ZSM-5 catalysts have been shown excellent SCR activity at the entire temperature range. However, the exhaust gases of Diesel vehicles and some plants contain alkali metal compounds after dust removal, which can have a severe poisoning effect on the activity of Fe-Cu-ZSM-5 catalyst. Na and K poisoned catalysts were prepared by wet impregnation method and were tested in the NH₃-SCR reaction of NO abatement. XRD, SEM and N₂physisorption characterization results showed that alkali metals introduction did not decrease the crystallinity and textural properties (specific surface area and pore volume) of parent zeolite. STEM-EDX and NH₃-TPD showed that Na promotes the agglomeration of iron and copper particles and neutralizes strong acid sites leading to a remarkable deterioration of Na-Fe-Cu-Z catalyst at high temperature range since it is well recognized that the decrease of surface acidity is regarded as one of the main reasons for the deactivation of alkali poisoned catalysts. This study clearly shows that the K-resistance of Fe-Cu-Z was better than Na-resistance above 400 °C which can be attributed to the better strong acidity and dispersion of metallic species

of the resulting material after K deposit. Therefore, iron and especially copper are much less back exchanged in the presence of potassium than sodium.

Author Contributions: Project administration, I.M. and M.M.; Catalysts preparation, H.J. and C.P.; NH₃-SCR catalytic testing, H.J. and G.D.; SEM and STEM experiments performing, J.L.C and J.MO; UV-vis DRS and NH₃-TPD analysis performing, T.B.; XRD and N₂physisorption analysis performing, H.J. and C.P.; writing-original draft preparation, H.J.; writing-review and editing, G.D. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Conflicts of Interest: The authors declare no conflict of interest.

Data Availability Statements: All data generated or analysed during this study are included in this published article.

References

Beznis NV, Weckhuysen BM, Bitter JH (2010) Cu-ZSM-5 Zeolites for the Formation of Methanol from Methane and Oxygen: Probing the Active Sites and Spectator Species. *Catal Lett* 138: 14-22. <https://doi.org/10.1007/s10562-010-0380-6>

Bordiga S, Buzzoni R, Geobaldo F et al (1996) Structure and Reactivity of Framework and Extraframework Iron in Fe-Silicalite as Investigated by Spectroscopic and Physicochemical Methods. *J Catal* 158: 486-501. <https://doi.org/10.1006/jcat.1996.0048>

Chanquía CM, Sapag K, Rodríguez-Castellón E et al (2010) Nature and Location of Copper Nanospecies in Mesoporous Molecular Sieves. *Phys Chem Chem Phys* 114: 1481-1490. <https://doi.org/10.1021/jp9094529>

Chen G, Xiong S, Chen X et al (2021) Penetration of Arsenic and Deactivation of a Honeycomb V₂O₅-WO₃/TiO₂ Catalyst in a Glass Furnace. *Environ. Sci. Technol* 55: 11368-11374. <https://doi.org/10.1021/acs.est.1c01314>

Fan C, Chen Z, Pang L et al (2018) Steam and alkali resistant Cu-SSZ-13 catalyst for the selective catalytic reduction of NO_x in diesel exhaust. Chem Eng J 334: 344-354.

<https://doi.org/10.1016/j.cej.2017.09.181>

Feng C, Wang P, Liu X et al (2021) Alkali-Resistant Catalytic Reduction of NO_x via Naturally Coupling Active and Poisoning Sites. Environ. Sci. Technol 55: 11255-11264.

<https://doi.org/10.1021/acs.est.1c02061>

Jouini H, Mejri I, Martinez-Ortigosa J et al (2018a) Characterization and NH₃-SCR reactivity of Cu-Fe-ZSM-5 catalysts prepared by solid state ion exchange: The metal exchange order effect. Microporous Mesoporous Mater 260: 217-226. <https://doi.org/10.1016/j.micromeso.2017.10.051>

Jouini H, Mejri I, Martinez-Ortigosa J et al (2018b) Selective catalytic reduction of nitric oxide with ammonia over Fe-Cu modified highly silicated zeolites. Solid State Sci 84: 75-85.

<https://doi.org/10.1016/j.solidstatesciences.2018.08.008>

Jouini H, Martinez-Ortigosa J, Mejri I et al (2019) On the performance of Fe-Cu-ZSM-5 catalyst for the selective catalytic reduction of NO with NH₃: the influence of preparation method. Res Chem Intermed 45: 1057-1072. <https://doi.org/10.1007/s11164-018-3658-8>

Khodayari R, Odenbrand CUI (2001) Regeneration of commercial TiO₂-V₂O₅-WO₃ SCR catalysts used in bio fuel plants. Appl Catal B: Environ 30: 87-99. [https://doi.org/10.1016/S0926-3373\(00\)00227-7](https://doi.org/10.1016/S0926-3373(00)00227-7)

Kroöcher O, Elsener M (2008) Chemical deactivation of V₂O₅/WO₃-TiO₂ SCR catalysts by additives and impurities from fuels, lubrication oils, and urea solution: I. Catalytic studies. Appl Catal B: Environ 75: 215-227. <https://doi.org/10.1016/j.apcatb.2007.04.021>

Lisi L, Cimino S (2019) Catalyst Deactivation, Poisoning and Regeneration. Catalysts 9: 668.

<https://doi.org/10.3390/catal9080668>

Lisi L, Lasorella G, Malloggi S et al (2004) Single and combined deactivating effect of alkali metals and HCl on commercial SCR catalysts. Appl Catal B: Environ 50: 251-258.

<https://doi.org/10.1016/j.apcatb.2004.01.007>

Liu L, Wu X, Ma Y et al (2020) Deposition of Potassium Salts on Soot Oxidation Activity of Cu-SSZ-13 as a SCR Catalyst: Laboratory Study. Catal Surv Asia 24: 250-258.

<https://doi.org/10.1007/s10563-020-09304-6>

Madia G, Koebel M, Elsener M et al (2002) Side Reactions in the Selective Catalytic Reduction of NO_x with Various NO₂ Fractions. *Ind Eng Chem Res* 41: 4008-4015. <https://doi.org/10.1021/ie020054c>

Mehsein K, Delahay G et al (2019) Comparison of Vehicle Aged SCR Catalyst on a Particulate Filter (SCRF) with Oven Aged Equivalent. *IJAME* 16(3) :6918-6930. <https://doi.org/10.15282/ijame.16.3.2019.07.0519>

Ming S, Pang L, Chen Z et al (2020) Insight into SO₂ poisoning over Cu-SAPO-18 used for NH₃-SCR. *Micropor Mesopor Mater* 303: 110294. <https://doi.org/10.1016/j.micromeso.2020.110294>

Peng Y, Li J, Shi W et al (2012) Design Strategies for Development of SCR Catalyst: Improvement of Alkali Poisoning Resistance and Novel Regeneration Method. *Environ Sci Technol* 46 : 12623–12629. <https://doi.org/10.1021/es302857a>

Pérez-Ramírez J, Groen JC, et al (2005) Evolution of isomorphously substituted iron zeolites during activation: comparison of Fe-beta and Fe-ZSM-5. *J Catal* 232: 318-334. <https://doi.org/10.1016/j.jcat.2005.03.018>

Qi GS, Yang RT (2005) Selective catalytic oxidation (SCO) of ammonia to nitrogen over Fe/ZSM-5 catalysts. *Appl Catal A: Gen* 287: 25-33. <https://doi.org/10.1016/j.apcata.2005.03.006>

Sjövall H, Olsson L, Fridell E et al (2006) Selective catalytic reduction of NO_x with NH₃ over Cu-ZSM-5-The effect of changing the gas composition. *Appl Catal B: Environ* 64: 180-188. <https://doi.org/10.1016/j.apcatb.2005.12.003>

Sun K, Fan F, Xia H et al (2008) Framework Fe Ions in Fe-ZSM-5 Zeolite Studied by UV Resonance Raman Spectroscopy and Density Functional Theory Calculations. *J Phys Chem C* 112: 16036-16041. <https://doi.org/10.1021/jp802955s>

Tarot M-L, Iojoiu E E et al (2019) Influence of Na, P and (Na + P) poisoning on a model copper-ferrierite NH₃- SCR catalyst. *Appl Catal B: Environ* 250: 355–368. <https://doi.org/10.1016/j.apcatb.2019.03.044>

Wu Q, Chen X, Mi J et al (2021) The Absence of Oxygen in Sulfation Promotes the Performance of the Sulfated CeO₂ Catalyst for Low-Temperature Selective Catalytic Reduction of NO_x by NH₃: Redox Property versus Acidity. *ACS Sustainable Chem Eng* 9: 967-979. <https://doi.org/10.1021/acssuschemeng.0c08427>

Wu Q, Fan C, Wang Y, et al (2022) Direct incorporating small amount of Ce (III) in Cu-SAPO-18 catalysts for enhanced low-temperature NH₃-SCR activity: Influence on Cu distribution and Si coordination. *Chem Eng J* 435: 134890. <https://doi.org/10.1016/j.cej.2022.134890>

Xiong S, Chen J, Huang N et al (2020) The poisoning mechanism of gaseous HCl on low-temperature SCR catalysts: MnO_x-CeO₂ as an example. *Appl Catal B: Environ* 267: 118668. <https://doi.org/10.1016/j.apcatb.2020.118668>

Zhang P, Wang P, Chen A et al (2021) Alkali-Resistant Catalytic Reduction of NO_x by Using Ce-O-B Alkali-Capture Sites. *Environ. Sci. Technol* 55: 11970-11978. <https://doi.org/10.1021/acs.est.1c02882>

Zhao Y, Shi L, Shen Y et al (2022) Self-Defense Effects of Ti-Modified Attapulgite for Alkali-Resistant NO_x Catalytic Reduction. *Environ. Sci. Technol* 56: 4386-4395. <https://doi.org/10.1021/acs.est.1c07996>

Zhou G, Maitarad P, Wang P et al (2020) Alkali-Resistant NO_x Reduction over SCR Catalysts via Boosting NH₃ Adsorption Rates by In Situ Constructing the Sacrificed Sites. *Environ. Sci. Technol* 54: 13314-13321. <https://doi.org/10.1021/acs.est.0c04536>

Zhu N, Shan Y, Shan W et al (2020) Distinct NO₂ Effects on Cu-SSZ-13 and Cu-SSZ-39 in the Selective Catalytic Reduction of NO_x with NH₃. *Environ. Sci. Technol* 54: 15499-15506. <https://doi.org/10.1021/acs.est.0c06256>