



**HAL**  
open science

# Doping induced stable room temperature dual emission from gadolinium doped vacancy ordered double halide perovskite, Gd:Cs<sub>2</sub>SnCl<sub>6</sub>

Aadil Ahmad Bhat, Nitesh Singh, Rajesh V Nair, Erik Dujardin, Jadab Sharma

► **To cite this version:**

Aadil Ahmad Bhat, Nitesh Singh, Rajesh V Nair, Erik Dujardin, Jadab Sharma. Doping induced stable room temperature dual emission from gadolinium doped vacancy ordered double halide perovskite, Gd:Cs<sub>2</sub>SnCl<sub>6</sub>. *Optical Materials*, 2023, 141, pp.113937. 10.1016/j.optmat.2023.113937. hal-03781995

**HAL Id: hal-03781995**

**<https://hal.science/hal-03781995>**

Submitted on 20 Sep 2022

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

1  
2  
3  
4 **Doping induced stable room temperature dual emission from gadolinium**  
5 **doped vacancy ordered double halide perovskite, Gd:Cs<sub>2</sub>SnCl<sub>6</sub>**  
6  
7  
8

9  
10 Aadil Ahmad Bhat<sup>1</sup>, Nitesh Singh<sup>2</sup>, Rajesh V. Nair<sup>2</sup>, Erik Dujardin<sup>3</sup> and Jadab Sharma<sup>1\*</sup>  
11

12  
13 Aadil Ahmad Bhat (ID 0000-0002-7510-9663), Dr. Jadab Sharma (ID 0000-0003-3138-8530)  
14

15 <sup>1</sup>Centre for Nanoscience and Nanotechnology, Panjab University, Chandigarh-160014, Chandigarh,  
16

17 India  
18

19 \*E-mail: jadabs@pu.ac.in  
20  
21

22  
23 Nitesh Singh (ID 0000-0003-2416-7406), Dr. Rajesh V. Nair (ID 0000-0001-5564-7264)  
24

25 <sup>2</sup>Department of Physics, Indian Institute of Technology Ropar, Rupnagar-140001, Punjab, India  
26

27 Dr. Erik Dujardin (ID 0000-0001-7242-9250)  
28

29 <sup>3</sup>Laboratoire Interdisciplinaire Carnot de Bourgogne (ICB), CNRS UMR 6303, Université  
30

31 Bourgogne Franche-Comté  
32

33 9 avenue A. Savary - BP 47870 - 21078 Dijon Cedex - FRANCE  
34  
35  
36

37 **Conflict of interest disclosure**  
38

39 The authors declare no conflict of interest.  
40  
41  
42  
43

44 **Abstract**  
45

46 The recent advancement in bandgap engineering through controlled doping has widened the prospect  
47 of vacancy ordered double halide perovskites (VO DHPs) by conferring them with designable  
48 optoelectronic properties. Here, we report synthesis of Gd doped Cs<sub>2</sub>SnCl<sub>6</sub> via a simple  
49 solvothermal method. Gd<sup>3+</sup> ions doping lowers the band gap from 3.8 eV to 2.8 eV and facilitates  
50 stable room temperature dual PL emission centered at 440 nm and 610 nm. The macroscopic  
51 emission process is well supported by the confocal PL emission studies on isolated crystallites.  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 Both the pristine ( $\text{Cs}_2\text{SnCl}_6$ ) and  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$  exhibit crystalline cubic structure with  $Fm\bar{3}m$  space  
5  
6 group. Rietveld refinement correlates well with the cubic phase and the analysis of (220) XRD  
7  
8 peak validates the existence of a secondary crystalline phase. SEM studies confirm the anisotropic  
9  
10 growth, forming large micron sized octahedral structures of pristine ( $> 20 \mu\text{m}$ ) and  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$   
11  
12 ( $< 5 \mu\text{m}$ ). This study enhances the experimental understanding of hitherto unknown dual PL  
13  
14 emission properties of  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$  having implication in quantum photonics leaving a scope for  
15  
16 detail theoretical study on the origin of the electronic transitions.  
17  
18  
19  
20  
21  
22  
23  
24

### 25 **Keywords**

26  
27  
28 vacancy ordered (VO) double halide perovskites (DHP), band gap engineering,  
29  
30 photoluminescence (PL) emission, confocal PL spectroscopy.  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

## 1. Introduction

Nano-and micro-crystalline lead halide perovskites (LHP) are considered to be the most prominent and promising photonic materials for optoelectronic and photovoltaic applications.<sup>1-5</sup> Among them, methyl ammonium lead halide perovskites ( $\text{CH}_3\text{NH}_3\text{PbX}_3$ )<sup>5,6</sup> and cesium lead halide perovskites ( $\text{CsPbX}_3$ ),<sup>7,8</sup> where  $X = \text{Cl}, \text{Br}, \text{I}$  have been extensively studied recently due to their exceptional physical and chemical properties. However, in spite of their exciting properties, the commercial prospects of these materials is seriously hampered by the environmental concern of Pb toxicity and their inherent instability. To overcome it, Pb is being replaced with elements such as Sb, Sn, In, Bi, etc.<sup>9,10</sup> For instance, two  $\text{Pb}^{2+}$  ions can be replaced by one monovalent metal ion ( $\text{M}^+$ :  $\text{Li}^+, \text{Ag}^+, \text{Na}^+, \text{K}^+$ , etc.) and one trivalent metal ion ( $\text{M}^{3+}$ :  $\text{In}^{3+}, \text{Sb}^{3+}, \text{Bi}^{3+}$ ) by co-substitution method with the structure  $\text{Cs}_2\text{M}^+\text{M}^{3+}\text{X}_6$  ( $X = \text{Cl}, \text{Br}, \text{I}$ ).<sup>11-13</sup> Another feasible strategy is replacement of  $\text{Pb}^{2+}$  with  $\text{Sn}^{2+}$  ions, but it also undergoes oxidation to  $\text{Sn}^{4+}$ .<sup>14</sup> Interestingly, a new class of materials with the stable structure  $\text{Cs}_2\text{SnX}_6$ , known as vacancy ordered double halide perovskites (VO DHP), has emerged by direct replacement of  $\text{Pb}^{2+}$  with  $\text{Sn}^{4+}$  ions.<sup>15</sup>

The peculiar crystal structure of  $\text{Cs}_2\text{SnX}_6$  presents vacancies in B-sites of regular  $\text{ABX}_3$  perovskites to form corner sharing  $[\text{BX}_6]$  octahedra that shows good thermal and structural stability.<sup>16-19</sup> In this homologous family,  $\text{Cs}_2\text{SnI}_6$  shows ambipolar characteristics due to p-type and n-type doping depending on cesium or iodide vacancies with an impressive direct band gap of  $\sim 1.3$  eV and good defect tolerance towards vacancy states.<sup>16,20-22</sup> In contrast,  $\text{Cs}_2\text{SnCl}_6$  does not show similar optoelectronic properties, thanks to the large band gap ( $> 3.8$  eV), despite exhibiting good thermal and structural stability.<sup>17-19</sup>

Recently, bandgap engineering upon doping has widen the prospect of these materials by conferring them with designable optoelectronic properties.<sup>23</sup> For example, blue<sup>24</sup>, yellow and white<sup>25</sup> emission from  $\text{Cs}_2\text{SnCl}_6$  nanocrystals doped with  $\text{Bi}^{3+}$ ,  $\text{Te}^{4+}$ , and  $\text{Sb}^{3+}$  ions, respectively


1  
2  
3  
4 have been reported with high quantum yield. Similarly, careful control of the concentration of  $\text{Sn}^{2+}$   
5  
6 in  $\text{Bi}^{3+}$ -doped  $\text{Cs}_2\text{SnCl}_6$  leads to blue emission,<sup>24</sup> while  $\text{Sb}^{3+}$  doping produces orange emission.<sup>26</sup>  
7  
8 At cryogenic temperature,  $\text{Sb}^{3+}$  doped  $\text{Cs}_2\text{SnCl}_6$  shows two emission peaks, while  $\text{Bi}^{3+}$  doping  
9  
10 shows only a single peak.<sup>27</sup> Very recently, significant alteration of the structural characteristics of  
11  
12 VO DHPs has been shown by applied pressure opening another leverage to modulate  
13  
14 optoelectronic properties.<sup>28</sup> Thus, renewed research interest on VO DHPs has emerged mainly due  
15  
16 to their untapped photophysical properties as a result of controlled alteration of crystal structure  
17  
18 and/or electronic structure by band gap engineering through doping.  
19  
20  
21  
22  
23

24  
25 Herein, we report the anisotropic growth of microcrystalline Gd-doped  $\text{Cs}_2\text{SnCl}_6$  that shows stable  
26  
27 dual PL emission even at room temperature. The macroscopic PL emission is corroborated by the  
28  
29 confocal PL emission studies for isolated crystallites. Our study opens up the possibility of  
30  
31 lanthanide doping in  $\text{Cs}_2\text{SnCl}_6$  that requires in-depth theoretical understanding due to the lesser  
32  
33 explored complex electronic transitions involving electrons in f-orbitals.  
34  
35  
36  
37

## 38 **2. Results and Discussion**


39  
40 The crystal structures of  $\text{Cs}_2\text{SnCl}_6$  and Gd-doped  $\text{Cs}_2\text{SnCl}_6$  ( $\text{Gd}:\text{Cs}_2\text{SnCl}_6$ ) were assessed by  
41  
42 powder X-ray diffraction studies as shown in Figure 1a. The emergence of the crystalline cubic  
43  
44 phase is well correlated with the JCPDS (card No. # 9023) which shows the space symmetry of  
45  
46  $Fm\bar{3}m$  and the diffraction patterns can be indexed to (111), (200), (220), (311), (222), (400), etc.  
47  
48 planes of  $\text{Cs}_2\text{SnCl}_6$  crystalline phase.<sup>24</sup> Figure 1b shows the representative crystal structures of  
49  
50  $\text{Cs}_2\text{SnCl}_6$  and  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$ . It is evident from the XRD patterns that the as-synthesized materials  
51  
52 have no crystalline impurity diffractions. The Rietveld refinement for  $\text{Cs}_2\text{SnCl}_6$  and 3 %  
53  
54  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$  are shown in **Figure 1c & d**, respectively with a very low  $\chi^2$  value (< 4.5) indicating  
55  
56 a good agreement between simulated and experimental XRD patterns (Rietveld refinements for  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 1% Gd:Cs<sub>2</sub>SnCl<sub>6</sub> and 2 % Gd:Cs<sub>2</sub>SnCl<sub>6</sub> are given as supporting information, SI Figure-S1). The  
5  
6 XRD patterns for Gd:Cs<sub>2</sub>SnCl<sub>6</sub> are identical to that of pristine sample and the peak positions also  
7  
8 coincide (both experimental and simulated) showing no additional diffraction peaks except the  
9  
10 splitting of the peak corresponding to (220) plane and a minor shift towards lower 2 $\Theta$  value (Figure  
11  
12 1e). The deviation in the (220) diffraction peak is due to the marginal difference in the ionic radii  
13  
14 of Gd<sup>3+</sup> (0.62 Å) and Sn<sup>4+</sup> (0.69 Å) ions in the lattice and creation of halide vacancies arising from  
15  
16 the charge disparity.<sup>20,24,29</sup> It is apparent that, as the molar percentage (number of Gd<sup>3+</sup> ions in the  
17  
18 crystal) is increased, the crystal structure is deformed and a secondary phase appears. The obtained  
19  
20 lattice parameters (SI, Table-S1) are in good agreement with the previous reports.<sup>24</sup> No noticeable  
21  
22 degradation could be detected in the XRD patterns when samples were stored for a couple of  
23  
24 months, thus suggesting a long term stability in ambient conditions (SI, Figure- S2).

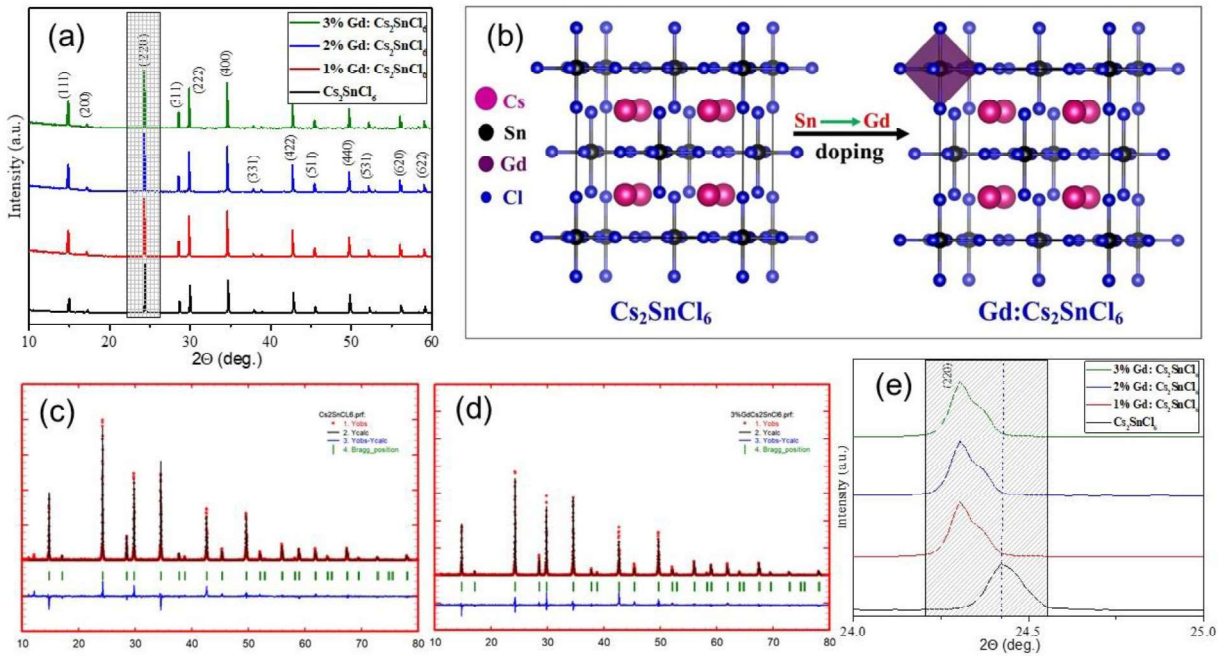

54  
55 **Figure 1.** (a) XRD patterns of Cs<sub>2</sub>SnCl<sub>6</sub> and Gd:Cs<sub>2</sub>SnCl<sub>6</sub> at different molar doping percentages. (b) Crystal structure  
56 of Cs<sub>2</sub>SnCl<sub>6</sub> and Gd:Cs<sub>2</sub>SnCl<sub>6</sub>. Rietveld refinement for (c) Cs<sub>2</sub>SnCl<sub>6</sub> and (d) 3 % Gd: Cs<sub>2</sub>SnCl<sub>6</sub>. (e) Expanded view of  
57 the XRD peak corresponding to (220) crystal plane of Cs<sub>2</sub>SnCl<sub>6</sub> and Gd:Cs<sub>2</sub>SnCl<sub>6</sub>. Cs<sub>2</sub>SnCl<sub>6</sub>, 1% Gd:Cs<sub>2</sub>SnCl<sub>6</sub>, 2%  
58 Gd:Cs<sub>2</sub>SnCl<sub>6</sub> and 3% Gd:Cs<sub>2</sub>SnCl<sub>6</sub> represent pristine and molar percentages of Gd-doping during the synthesis,  
59 respectively. Rietveld refinement plots for 1 % and 2% Gd:Cs<sub>2</sub>SnCl<sub>6</sub> are given in supporting information (Figure S1).

The UV-vis absorption and PL spectra were recorded to shed light on the effect of doping on the photo-physical properties. Figure 2a & b shows the UV-vis absorption spectra and corresponding Tauc plots for pristine and Gd doped  $\text{Cs}_2\text{SnCl}_6$ , respectively. The changes in the absorption band edge for doped samples is evident from the UV-visible spectra which extends beyond 320 nm recorded for pristine sample. As the doping percentage increases, the optical band gap extracted from Figure 2b decreases from 3.8 eV ( $\text{Cs}_2\text{SnCl}_6$ ) to 3.6 eV (1 % Gd: $\text{Cs}_2\text{SnCl}_6$ ), 3.4 eV (2 % Gd: $\text{Cs}_2\text{SnCl}_6$ ), and 2.8 eV (3 % Gd: $\text{Cs}_2\text{SnCl}_6$ ). Thus, the Gd-doping has a significant effect on the electronic band structure. The DFT calculations using mBJ+ SOC approximations within Wien2K code for the electronic structure of  $\text{Cs}_2\text{SnCl}_6$  also show a direct band gap of 3.88 eV at  $\Gamma$  (Gamma) point of the Brillouin zone.<sup>30</sup>

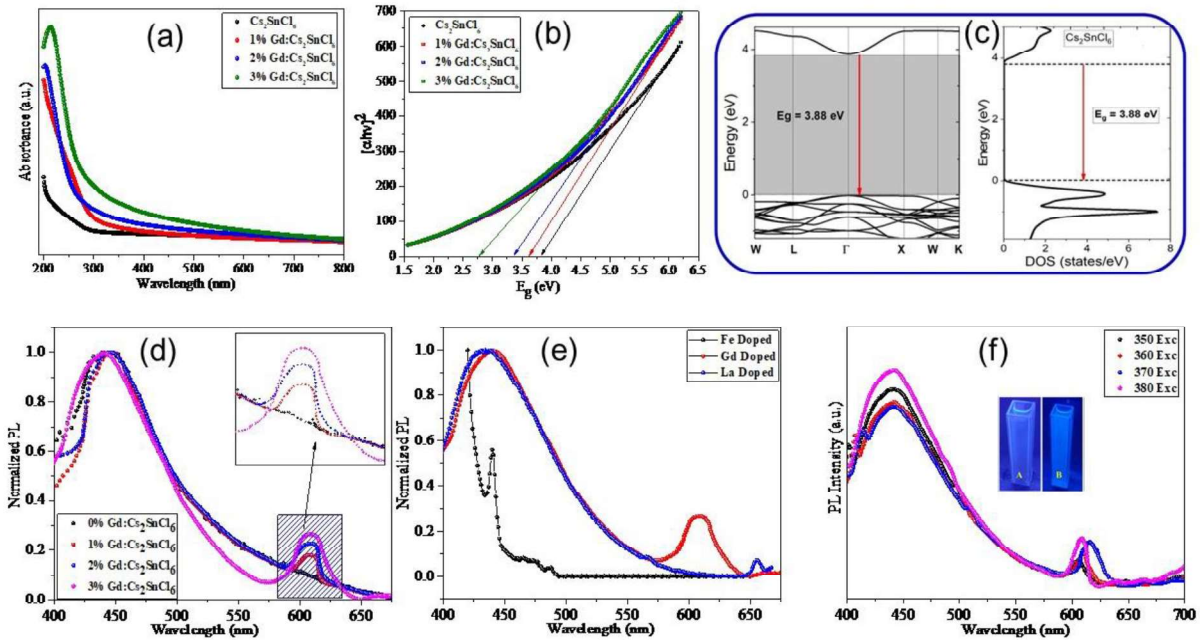

**Figure 2.** (a) UV-vis spectra of  $\text{Cs}_2\text{SnCl}_6$  and Gd: $\text{Cs}_2\text{SnCl}_6$  at different doping percentages and (b) the corresponding Tauc plots for band gap estimation. (c) Electronic structure and band gap estimated using DFT calculation for  $\text{Cs}_2\text{SnCl}_6$ . (d) PL spectra of pristine and Gd doped  $\text{Cs}_2\text{SnCl}_6$ . (e) PL spectra of La, Gd, and Fe doped  $\text{Cs}_2\text{SnCl}_6$ . (f) PL spectra of 3 % Gd: $\text{Cs}_2\text{SnCl}_6$  at various excitation wavelengths. Inset: Photograph of samples under UV-illumination of  $\text{Cs}_2\text{SnCl}_6$  (left) and 3% Gd: $\text{Cs}_2\text{SnCl}_6$  (right).  $\text{Cs}_2\text{SnCl}_6$ , 1% Gd: $\text{Cs}_2\text{SnCl}_6$ , 2% Gd: $\text{Cs}_2\text{SnCl}_6$  and 3% Gd: $\text{Cs}_2\text{SnCl}_6$  represent pristine and Gd-doped  $\text{Cs}_2\text{SnCl}_6$  at different molar doping percentages, respectively.


1  
2  
3  
4 Figure 2c shows that the conduction band minimum (mostly populated by Sn-S and Cl- $P_z$  states)  
5  
6 and valence band maximum (entirely populated by Cl- $P_{x-y}$  states) is located at the same symmetry  
7  
8 point. Figure 2d shows the PL spectra of pristine and Gd:Cs<sub>2</sub>SnCl<sub>6</sub>. Cs<sub>2</sub>SnCl<sub>6</sub> shows a  
9  
10 characteristics single emission peak at 440 nm, with a negligible shift towards low energy (from  
11  
12 438 to 440 nm) when excited at 365 nm.<sup>26</sup> The emission centered at 440 nm is asymmetric and has  
13  
14 an extended tail in the long wavelength region indicating that it originates from the defect states  
15  
16 rather than from the free excitons of Cs<sub>2</sub>SnCl<sub>6</sub>. The origin of the 438 nm emission reported earlier  
17  
18 for Cs<sub>2</sub>SnCl<sub>6</sub> is due to the defect states in nanocrystals,<sup>26</sup> while the present emission is from the  
19  
20 bulk microcrystals (> 20  $\mu$ m, from SEM studies discussed later). As evidenced from the  
21  
22 crystallographic results, Gd<sup>3+</sup> is substituted for Sn<sup>4+</sup> site that leads to vacancy states, while charge  
23  
24 balance is maintained through nonstoichiometric compositions. Further, the elemental analysis and  
25  
26 XPS studies confirm the successful doping by Gd<sup>3+</sup> ions (discussed in succeeding sections). Unlike  
27  
28 the Sb<sup>3+</sup> doped Cs<sub>2</sub>SnCl<sub>6</sub>, 3% Gd:Cs<sub>2</sub>SnCl<sub>6</sub> does not induce noticeable color change under UV  
29  
30 illumination. However, Figure 2d clearly shows the emergence of an additional PL emission peak  
31  
32 which is centered at *ca.* 610 nm. The intensity of the 2<sup>nd</sup> emission peak increases with the increase  
33  
34 of the doping percentage (inset of Figure 2d). To clarify the emergence of the 2<sup>nd</sup> emission, we  
35  
36 prepared La and Fe- doped DHPs. Interestingly, 5% La:Cs<sub>2</sub>SnCl<sub>6</sub> also exhibits a low intensity  
37  
38 second emission peak at *ca.* 650 nm which is weaker than the emission peak of Gd<sup>3+</sup>- doped DHP,  
39  
40 while 3% Fe:Cs<sub>2</sub>SnCl<sub>6</sub> does not show any second emission peak though showing a distinctly  
41  
42 different PL emission spectrum (Figure 2e). The low intensity emission from La-doped DHP  
43  
44 indicates that excitation from the 4f<sup>0</sup> electron is weak (in the absence of rarely populated 4f  
45  
46 orbitals) in comparison to the half field 4f<sup>7</sup>-electrons of Gd<sup>3+</sup>- doped DHP. This dual emission  
47  
48 becomes intense when excited at 380 nm (Figure 2f) which is different from the earlier reports on  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



1  
2  
3  
4 doped DHPs where 2<sup>nd</sup> emission is associated with a change in color, while Gd<sup>3+</sup>- doped DHP  
5  
6 remains blue under UV-illumination at 365 nm. The photographs of the samples under UV-  
7  
8 illumination are given as inset in Figure 2f.  
9

10  
11 The persistence of the 2nd emission peak at 610 nm when varying of the excitation wavelength  
12  
13 from 350 -380 nm (Figure 2f), indicates that this 2nd emission originates from the Gd<sup>3+</sup> doping  
14  
15 rather than overtones of the excitation. It is evident that Gd<sup>3+</sup>- doped DHP exhibits photo-physical  
16  
17 characteristics different than the emission reported earlier for Sb<sup>3+</sup>, Bi<sup>3+</sup>, or other transition metals  
18  
19 doping where p orbitals contribute towards the electronic transitions corresponding to singlet  
20  
21 (<sup>1</sup>T<sub>1u</sub>\* → <sup>1</sup>A<sub>1g</sub>) and triplet (<sup>3</sup>T<sub>1u</sub>\* → <sup>1</sup>A<sub>1g</sub>) emissions (such as Bi<sup>3+</sup> doping) due to a stronger spin  
22  
23 orbit coupling<sup>27,29,31</sup> promoted by triplet self-trapped excitations.<sup>26</sup> A recent study showed that a  
24  
25 combination of John-Teller distortion and spin-orbit coupling is responsible for the dual peak at  
26  
27 cryogenic temperature, while spin-orbit coupling dominates over John-Teller distortion, resulting  
28  
29 in a single peak in Bi<sup>3+</sup> doped Cs<sub>2</sub>SnCl<sub>6</sub>.<sup>27</sup> Similarly, the vibrational progression in emission  
30  
31 spectra at low temperature due to the John-Teller distortion was reported back in 1988 for Cs<sub>2</sub>MCl<sub>6</sub>  
32  
33 (M= Zr, Sn).<sup>32</sup> Despite the clear understanding of the involvement of p orbitals contributing  
34  
35 significantly in the origin of band gap and emission process,<sup>20,31,33</sup> electronic transitions in  
36  
37 lanthanide doped DHPs involve the 4f-orbitals<sup>34</sup> of the dopant, resulting in more complex  
38  
39 excitation pathways with 4f → 4f transitions, as modeled by the Judd-Ofelt theory, which was later  
40  
41 extended to 4f → 5d transitions.<sup>35,36</sup> In general, this type of doping presents broad emission from  
42  
43 the parity-allowed transition 4f<sup>6</sup>5d<sup>1</sup> → 4f<sup>7</sup>, which presents wide-emission range in the blue-green-  
44  
45 yellow or red band reported for simple lanthanide ions.<sup>37,38</sup> The replacement of Sn<sup>4+</sup> with Gd<sup>3+</sup> in  
46  
47 the crystal lattice forms molecular orbitals involving Gd, Sn, and Cl that complicates the estimation  
48  
49 of the electronic band structure responsible for the emission sans a corroboration by theoretical  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

investigation. However, further insights are obtained from the confocal PL imaging of isolated individual emitters and their spectroscopic studies as discussed in the following section.

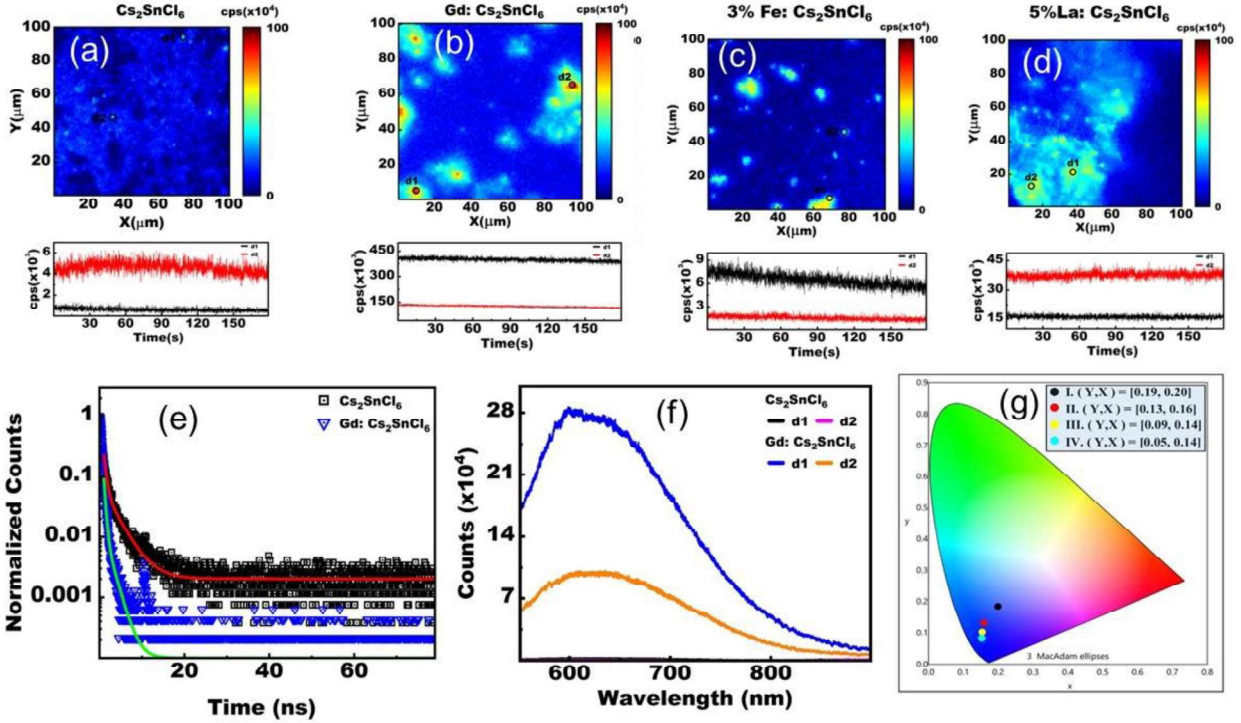

**Figure 3.** The confocal map (above) and time trace of photons (below) for (a)  $\text{Cs}_2\text{SnCl}_6$ , (b) 3 %  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$ , (c) 3 %  $\text{Fe}:\text{Cs}_2\text{SnCl}_6$  and (d) 5 %  $\text{La}:\text{Cs}_2\text{SnCl}_6$ . (e) The PL decay curve of pristine and doped DHPs. (f) PL spectra of  $\text{Cs}_2\text{SnCl}_6$  and 3 %  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$  recorded at selective points of d1 & d2 on the confocal images of the respective DHPs. (g) CIE diagram for pristine and doped DHPs. Coordinates for points I, II, III, and IV represent  $\text{Cs}_2\text{SnCl}_6$ , 1%  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$ , 2%  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$ , and 3%  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$ , respectively.

In order to carry out confocal imaging studies, the pristine and  $\text{Gd}^{3+}$ -doped  $\text{Cs}_2\text{SnCl}_6$  were spread on glass coverslips by drop casting method. All the data presented henceforth are for  $\text{Cs}_2\text{SnCl}_6$  and 3 %  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$ , unless mentioned otherwise. Figure 3a and b shows the confocal image of pristine and  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$  with a time trace of the photon count intensity (below the confocal map), respectively. The confocal image in Figure 3b shows emission hotspots for  $\text{Gd}:\text{Cs}_2\text{SnCl}_6$  from where the photon counts is large, which is absent for the pristine sample (Figure 3a). The data are collected from the emitters located at points d1 and d2 on the confocal image. The time trace shows

1  
2  
3  
4 that the emission is stable at room temperature and does not get photo-bleached which is a good  
5  
6 signature of emitters useful for quantum photonic and lasing applications.<sup>39,40</sup>  
7  
8

9 To verify the emission process, confocal emission images were also recorded for 3% Fe:Cs<sub>2</sub>SnCl<sub>6</sub>  
10 and 5% La:Cs<sub>2</sub>SnCl<sub>6</sub>. Confocal maps of emitters clearly demonstrate that there was no significant  
11 emission from Fe:Cs<sub>2</sub>SnCl<sub>6</sub> (Figure 3c), while La:Cs<sub>2</sub>SnCl<sub>6</sub> shows emission with lesser photon  
12 counts (Figure 3d). The corresponding decay life time and PL spectra are given as supporting  
13 information (Figure-S3). It is important to note that minor photon counts (< 9000) recorded for  
14 Cs<sub>2</sub>SnCl<sub>6</sub> and Fe:Cs<sub>2</sub>SnCl<sub>6</sub> may arise due to scattering. Figure 3e and f shows the PL decay and  
15 intensity curves for pristine and Gd:Cs<sub>2</sub>SnCl<sub>6</sub> originating from isolated individual crystallites. To  
16 estimate the PL decay dynamics, experimental data are fitted with a second exponential decay  
17 function corresponding to radiative and non-radiative decay process given as:  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30


$$31 \quad y = A_1 e^{-x/t_1} + A_2 e^{-x/t_2} \quad \dots (1)$$

32  
33  
34  
35 where t<sub>1</sub> is the lifetime corresponding to the fast-decaying component with A<sub>1</sub> amplitude and t<sub>2</sub>  
36  
37 corresponds to the slow-decaying component and is related to the tail of the curve with A<sub>2</sub>  
38  
39 amplitude (y corresponds to entity on y axis i.e. counts and x corresponds to entity on x axis i.e.  
40  
41 delay time). The average lifetime is given by the formula:  
42  
43  
44

$$45 \quad \tau_{avg} = \frac{A_1 t_1}{A_1 t_1 + A_2 t_2} t_1 + \frac{A_2 t_2}{A_1 t_1 + A_2 t_2} t_2 \quad \dots (2)$$

46  
47  
48  
49 The doped samples show lower lifetime measured for the 2<sup>nd</sup> emission (excitation at 532 nm by  
50  
51 pulsed diode laser) than the pristine sample (Figure 3e). It indicates that the population of the  
52  
53 excited states decreases rapidly (< 1 ns) through a faster radiative decay process for doped  
54  
55 Cs<sub>2</sub>SnCl<sub>6</sub>, while longer decay time recorded for the pristine sample is mostly from the scattering  
56  
57 process. The existence of two different decay lifetimes (other one monitored at 440 nm when  
58  
59  
60  
61  
62  
63  
64  
65

excited at 365 nm, Figure-S4, SI) clearly indicates the presence of two or more electronic excitation states of Gd:Cs<sub>2</sub>SnCl<sub>6</sub>. Figure 3f shows the PL spectra recorded for isolated crystallites of Gd:Cs<sub>2</sub>SnCl<sub>6</sub> located at points d1 and d2 on the corresponding confocal PL map while no significant emission is recorded for the pristine sample. The intense PL emission peak is centered around 610 nm, while the PL emission photon counts for the pristine sample are negligible (< 1000, mainly from scattering). Thus, confocal mapping from the individual emitters conclusively confirm the 2<sup>nd</sup> PL emission centered at *ca.* 610 nm from Gd:Cs<sub>2</sub>SnCl<sub>6</sub>.

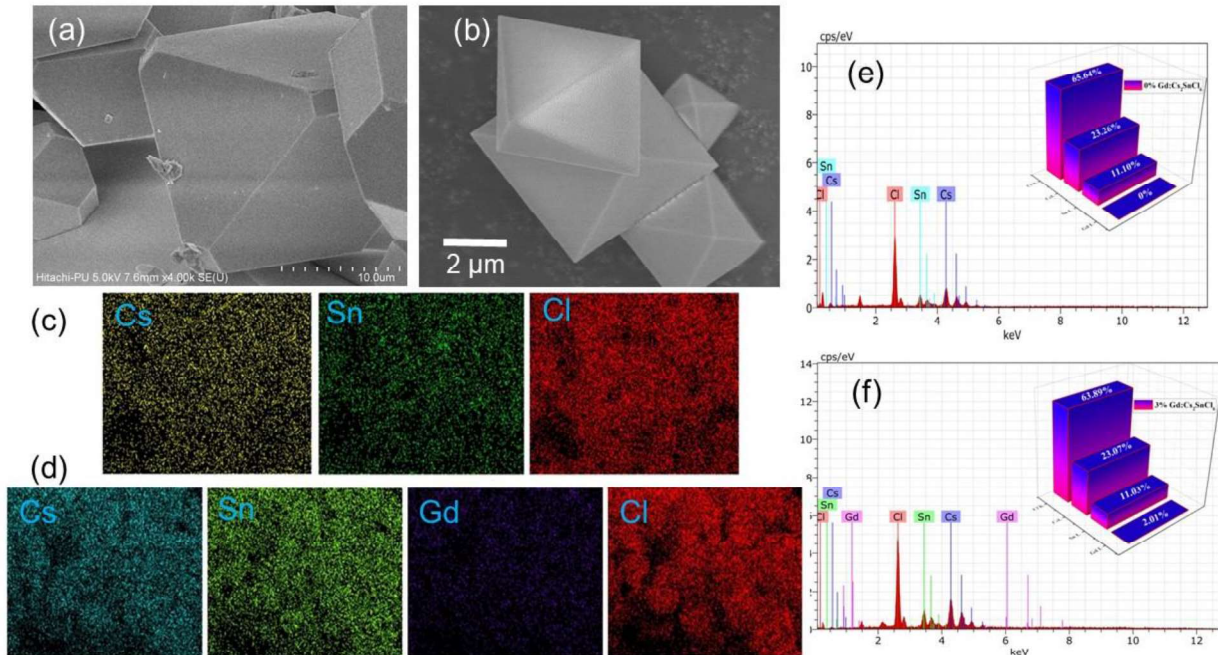

**Figure 4.** SEM micrographs of (a) Cs<sub>2</sub>SnCl<sub>6</sub> and (b) 3 % Gd:Cs<sub>2</sub>SnCl<sub>6</sub> DHPs. (c) Elemental mapping for (c) Cs<sub>2</sub>SnCl<sub>6</sub> and (d) 3% Gd:Cs<sub>2</sub>SnCl<sub>6</sub>. EDS of (e) Cs<sub>2</sub>SnCl<sub>6</sub> and (f) 3% Gd:Cs<sub>2</sub>SnCl<sub>6</sub>. Inset: bar diagrams of atomic percentages.


The Commission Internationale de l'Éclairage (CIE) co-ordinates were determined to plot the CIE diagram using Osram software. Figure 3g shows the CIE diagram for pristine and doped Cs<sub>2</sub>SnCl<sub>6</sub>, while their coordinates are mentioned in the white zone of the figure. As the Gd-content increases, the coordinates marginally shift towards the blue region. Although we have a clear understanding

1  
2  
3  
4 on crystal structure and the PL emission, the morphology and elemental composition of the  
5  
6  
7 crystallites are yet to be studied.

8  
9  
10 Accordingly, SEM micrographs of pristine and Gd-doped  $\text{Cs}_2\text{SnCl}_6$  are shown in **Figure 4** along  
11  
12 with their elemental mapping and EDS profiles. It is evident from the SEM images that pristine  
13  
14 (Figure 4a) and Gd: $\text{Cs}_2\text{SnCl}_6$  (Figure 4b) show large micron sized crystals with truncated  
15  
16 octahedral shapes. The crystallite size ( $< 5 \mu\text{m}$ ) of Gd: $\text{Cs}_2\text{SnCl}_6$  is one fourth of the size to that of  
17  
18 the pristine DHPs ( $> 20 \mu\text{m}$ ). Similar large bulk crystals have been reported for multi-doped  
19  
20  $\text{Cs}_2\text{SnCl}_6$  synthesized by modified solution growth method.<sup>26,41</sup> Figure 4c and d shows the  
21  
22 elemental mappings for pristine and 3% Gd: $\text{Cs}_2\text{SnCl}_6$  DHPs, respectively. The elemental mapping  
23  
24 was carried out for isolated individual crystallites as well. All the elements are uniformly  
25  
26 distributed throughout the crystal structures. The distribution of elements depends on homogenous  
27  
28 nucleation of the crystal and effectiveness of the doping. The stoichiometry of the elemental  
29  
30 composition can be determined by the EDS technique. Figure 4e and f shows the EDS of pristine  
31  
32 and Gd: $\text{Cs}_2\text{SnCl}_6$ , respectively. The presence of  $\text{Gd}^{3+}$  is confirmed from both elemental mapping  
33  
34 and EDS of Gd: $\text{Cs}_2\text{SnCl}_6$ . The respective elemental compositions are given as inset in the form of  
35  
36 bar-diagrams. It is clear that no additional elements from the precursor impurity are present. The  
37  
38 elemental composition analysis is in agreement with the composition analysis from the empirical  
39  
40 formula of the pristine and Gd: $\text{Cs}_2\text{SnCl}_6$ . Similar results are obtained for 1% Gd: $\text{Cs}_2\text{SnCl}_6$  and 2%  
41  
42 Gd: $\text{Cs}_2\text{SnCl}_6$  (SI, Figure S5).

43  
44  
45 In addition, the confirmatory composition analysis was carried by XPS. Figure 5 shows the XPS  
46  
47 spectra of (a) Sn 3d, (b) Cl 2p, (c) Cs 3d, and (e) Gd 4d electrons for Gd: $\text{Cs}_2\text{SnCl}_6$ . XPS spectra  
48  
49 confirm the presence of Cs ( $3d_{5/2}$  724.1 and  $3d_{3/2}$  738.1 eV), Sn ( $3d_{5/2}$  487.4 and  $3d_{3/2}$  495.9 eV)  
50  
51 and Cl ( $2p_{3/2}$  198.6 and  $2p_{1/2}$  200.3 eV) in both pristine (Figure S6, SI) and Gd doped DHPs, while  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61

1  
2  
3  
4 the detection of 4d electrons ( $4d_{5/2}$  141.3 and  $4d_{3/2}$  150.6 eV) of  $Gd^{3+}$  confirms effective doping in  
5  
6  $Cs_2SnCl_6$ . The results are in agreement with the previous XPS studies on  $Cs_2SnCl_6$ .<sup>41</sup>  
7  
8  
9

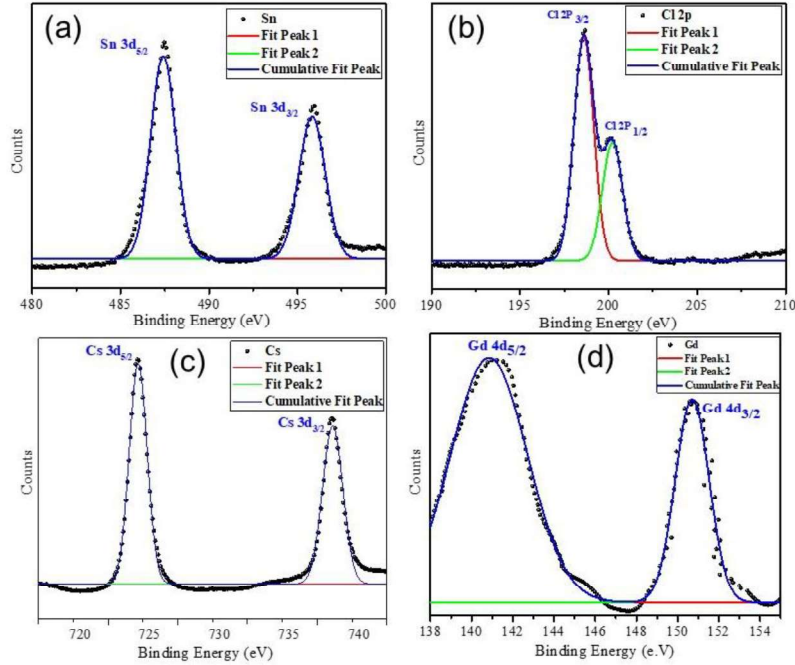

10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33 **Figure 5.** Deconvoluted XPS spectra of (a) Sn 3d, (b) Cl 2p, (c) Cs 3d, and (e) Gd 4d electrons for Gd: $Cs_2SnCl_6$  DHP.  
34 XPS profiles of Sn 3d, Cl 2p, and Cs 3d electrons for the pristine ( $Cs_2SnCl_6$ ) sample are given as supporting  
35 information (Figure-S6).  
36  
37

38  
39 The experimental evidences presented above confirm the successful synthesis of micron sized  
40  
41 crystallites of  $Cs_2SnCl_6$  and Gd doped  $Cs_2SnCl_6$ .  $Cs_2SnCl_6$  shows a single PL emission peak at  
42  
43 440 nm while Gd doping leads to dual emission indicating its application in blue emitting diode.  
44  
45  
46  
47

### 48 3. Conclusion

49  
50 In summary, we have successfully demonstrated the incorporation  $Gd^{3+}$  ions in the lead-free  
51  
52 double halide perovskite via a simple solvothermal method. Unlike the electronic band structure  
53  
54 of  $Cs_2SnCl_6$  when doped by elements with p and d-electrons, lanthanides present much more  
55  
56 complex system to simulate for the energy band structure due to the involvement of electrons in f-  
57  
58 orbitals and reports on such studies are rare. Despite the complexities involved, incorporation of  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4 the gadolinium ions into the crystal lattice enables us to tune the band gap up to 2.8 eV. PL studies  
5  
6 confirm stable room temperature dual emission at 440 nm and 610 nm from Gd:Cs<sub>2</sub>SnCl<sub>6</sub>. The  
7  
8 macroscopic PL emission is strongly supported by confocal PL emission studies. The confocal PL  
9  
10 emission from the individual crystallites is stable and does not undergo photo bleaching. This  
11  
12 study will have a significant ramification in developing materials for quantum photonics. Both the  
13  
14 pristine (Cs<sub>2</sub>SnCl<sub>6</sub>) and Gd:Cs<sub>2</sub>SnCl<sub>6</sub> DHPs exhibit cubic structure with  $Fm\bar{3}m$  space group  
15  
16 having good shelf-life stability. CIE plot shows that Gd:Cs<sub>2</sub>SnCl<sub>6</sub> is a better photonic material  
17  
18 suitable for blue LEDs than Cs<sub>2</sub>SnCl<sub>6</sub>. SEM studies show the octahedral geometry that results from  
19  
20 the anisotropic growth of Gd:Cs<sub>2</sub>SnCl<sub>6</sub>. In brief, our study enhances the experimental  
21  
22 understanding of the hitherto unknown stable dual emission properties at room temperature upon  
23  
24 lanthanide doping, leaving a scope for further experimental and theoretical study on the origin of  
25  
26 the electronic transitions in complex f-electron systems.  
27  
28  
29  
30  
31  
32

#### 33 **4. Experimental Section**

##### 34 **4.1 Chemicals**

35 Cesium chloride (CsCl, Loba Chemie), Tin chloride dihydrate (SnCl<sub>2</sub>.2H<sub>2</sub>O, Loba Chemie),  
36  
37 Hydrochloric acid (HCl, 36-38 %, AR grade Loba Chemie), Gadolinium nitrate hexahydrate  
38  
39 (Gd(NO<sub>3</sub>)<sub>3</sub>.6H<sub>2</sub>O, Sigma Aldrich), Ethanol (absolute, C<sub>2</sub>H<sub>6</sub>O, Loba Chemie) and Acetone (Loba  
40  
41 Chemie ) were used as received. Deionized water was used for cleansing glassware prior to acetone  
42  
43 rinsing and drying.  
44  
45  
46  
47  
48

##### 49 **4.2 Synthesis of Cs<sub>2</sub>SnCl<sub>6</sub> and Gd doped Cs<sub>2</sub>SnCl<sub>6</sub> DHP**

50  
51 2 mmol of CsCl (336.00 mg) and 1 mmol of SnCl<sub>2</sub>.2H<sub>2</sub>O (225.63 mg) were completely dissolved  
52  
53 in 5 mL of HCl (light yellow). After sonication for about 5 min, the reaction mixture turned milky  
54  
55 white. The mixture was transferred into a Teflon lined stainless steel autoclave (50 mL capacity)  
56  
57 followed by thermal treatment for about 10 hours at 180 °C. The autoclave was cooled down  
58  
59  
60  
61  
62

1  
2  
3  
4 naturally to ambient temperature and the precipitate was washed with ethanol and acetone several  
5  
6 times after removing the supernatant. The samples were then dried in a vacuum oven at 50 °C for  
7  
8 about 12 hours and stored at room temperature for characterization. Required molar quantities of  
9  
10 gadolinium nitrate were added during the synthesis of 1, 2, and 3 % Gd-doped Cs<sub>2</sub>SnCl<sub>6</sub> while  
11  
12 maintaining the other reaction conditions identical. Appropriate amounts of samples were  
13  
14 dispersed in ethanol/methanol before drop casting on substrates and for UV-visible spectroscopic  
15  
16 studies.  
17  
18  
19  
20

### 21 **4.3 Characterisation**

22  
23  
24 X-ray diffraction (XRD) studies were performed on a Rigaku Miniflex 600 diffractometer.  
25  
26 Scanning electron microscopy (SEM, JEOL Japan, Model No. JSM 6100) and energy-dispersive  
27  
28 spectroscopy (EDS, Ultra plus, Model No. 4322, ZEISS) were performed for morphological and  
29  
30 compositional analysis. Optical studies were carried out on a UV-visible spectrophotometer  
31  
32 (JASCO, V-770). For photoluminescence, a Horiba Fluorolog Fluorescence Spectrometer  
33  
34 (Fluorolog 3TCPS) was employed.  
35  
36  
37  
38

39 In order to carry out the confocal microscopy studies, the samples were spread on glass coverslips.  
40  
41 All the samples were dispersed in methanol and sonicated for 30 minutes before drop casting an  
42  
43 aliquot of 40 µl each. The confocal images were recorded using a home-built laser scanning  
44  
45 confocal microscope. The 532 nm pulsed diode laser (LDH-D-FA-530L, Picoquant, Germany)  
46  
47 was used to excite the sample. The excitation was done using a 60X magnification objective  
48  
49 (Nikon) with a numerical aperture (NA) of 0.95 to get maximum collection efficiency. The  
50  
51 coverslip containing the sample was mounted on an x-y-z translational stage controlled by  
52  
53 actuators (M-230.25; Physik Instruments) that allow the spatial scan of the sample. The whole  
54  
55 setup was controlled by a custom built LabVIEW software program. The setup worked in  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



1  
2  
3  
4 reflecting geometry thus, the emission was collected by the same objective and was accomplished  
5  
6 by the excitation pulse. In order to filter out the emission counts from excitation (mostly due to  
7  
8 scattering), a dichroic filter (DF) was used. The signal was further filtered using a long pass (LP).  
9  
10 The confocal map was recorded using a  $660 \pm 10$  nm spectral filter and the emission was coupled  
11  
12 with the multimode fiber. The fiber then brought the light to a highly sensitive single photon  
13  
14 avalanche photodiode (SPAD, Excelitas technology). The lifetime measurements were carried out  
15  
16 using a time-correlated single-photon counting unit (Hydraharp 400, PicoQuant).  
17  
18

19  
20 The photoluminescence (PL) spectra were recorded using EMCCD (Newton 970, Oxford  
21  
22 instruments). A grating with a groove density of 900 lines/mm was used for PL spectra acquisition.  
23  
24 The signals were acquired in EMCCD mode of the spectrometer for 0.1 sec with 20 accumulations.  
25  
26 It was observed that all samples got photo bleached for laser power above  $200 \mu\text{W}$ . Thus, for the  
27  
28 lifetime and PL measurement, the laser intensity was set below this threshold.  
29  
30  
31  
32  
33

### 34 **Supporting Information**

35  
36 Additional PL spectra, SEM images, XPS, and XRD data are provided as Supporting Information  
37  
38 and is available from the Wiley Online Library or from the author.  
39  
40

### 41 **Acknowledgements**

42  
43 This study was funded by CEFIPRA through the grant No. 6108-1. Authors acknowledge SAIF  
44  
45 Panjab University, Chandigarh; IIT Roorkee, Roorkee (for XRD, SEM, XPS, and EDS  
46  
47 measurements); SAIF Mahatma Gandhi University, Kottayam and SAIF IIT Bombay, Mumbai for  
48  
49 photoluminescence measurements. RVN acknowledges the financial support from DST-ICPS  
50  
51 (DST/ICPS/QuST/Theme-2/2019/General), DST-SERB (SB/SJF/2020-21/05), and Swarnajayanti  
52  
53 Fellowship (DST/SJF/PSA-01/2019-20). The authors are highly thankful to Dr. Shakeel Ahmad  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

## References

1. Fu, Y. *et al.* Metal halide perovskite nanostructures for optoelectronic applications and the study of physical properties. *Nat. Rev. Mater.* **4**, 169–188 (2019).
2. Snaith, H. J. & Hacke, P. Enabling reliability assessments of pre-commercial perovskite photovoltaics with lessons learned from industrial standards. *Nat. Energy* **3**, 459–465 (2018).
3. Li, Z. *et al.* Scalable fabrication of perovskite solar cells. *Nat. Rev. Mater.* **3**, 18017 (2018).
4. Stranks, S. D. & Snaith, H. J. Metal-halide perovskites for photovoltaic and light-emitting devices. *Nat. Nanotechnol.* **10**, 391–402 (2015).
5. Jena, A. K., Kulkarni, A. & Miyasaka, T. Halide Perovskite Photovoltaics: Background, Status, and Future Prospects. *Chem. Rev.* **119**, 3036–3103 (2019).
6. Saparov, B. & Mitzi, D. B. Organic–Inorganic Perovskites: Structural Versatility for Functional Materials Design. *Chem. Rev.* **116**, 4558–4596 (2016).
7. Yang, T., Li, F. & Zheng, R. Recent Progress on Cesium Lead Halide Perovskites for Photodetection Applications. *ACS Appl. Electron. Mater.* **1**, 1348–1366 (2019).
8. An, Y. *et al.* Structural Stability of Formamidinium- and Cesium-Based Halide Perovskites. *ACS Energy Lett.* **6**, 1942–1969 (2021).
9. Gao, Y., Pan, Y., Zhou, F., Niu, G. & Yan, C. Lead-free halide perovskites: a review of the structure–property relationship and applications in light emitting devices and radiation detectors. *J. Mater. Chem. A* **9**, 11931–11943 (2021).
10. Zhu, T., Yang, Y. & Gong, X. Recent Advancements and Challenges for Low-Toxicity Perovskite Materials. *ACS Appl. Mater. Interfaces* **12**, 26776–26811 (2020).
11. Han, P. & Han, K. Recent Advances in All-Inorganic Lead-Free Three-Dimensional Halide Double Perovskite Nanocrystals. *Energy & Fuels* **35**, 18871–18887 (2021).
12. Luo, J., Hu, M., Niu, G. & Tang, J. Lead-Free Halide Perovskites and Perovskite Variants as Phosphors toward Light-Emitting Applications. *ACS*

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- Appl. Mater. Interfaces* **11**, 31575–31584 (2019).
13. Pantaler, M. *et al.* Revealing Weak Dimensional Confinement Effects in Excitonic Silver/Bismuth Double Perovskites. *JACS Au* **2**, 136–149 (2022).
  14. Li, B. *et al.* Tin-Based Defects and Passivation Strategies in Tin-Related Perovskite Solar Cells. *ACS Energy Lett.* **5**, 3752–3772 (2020).
  15. Maughan, A. E., Ganose, A. M., Scanlon, D. O. & Neilson, J. R. Perspectives and Design Principles of Vacancy-Ordered Double Perovskite Halide Semiconductors. *Chem. Mater.* **31**, 1184–1195 (2019).
  16. Maughan, A. E. *et al.* Defect Tolerance to Intolerance in the Vacancy-Ordered Double Perovskite Semiconductors Cs<sub>2</sub>SnI<sub>6</sub> and Cs<sub>2</sub>TeI<sub>6</sub>. *J. Am. Chem. Soc.* **138**, 8453–8464 (2016).
  17. Huang, H.-M., Jiang, Z.-Y. & Luo, S.-J. First-principles investigations on the mechanical, thermal, electronic, and optical properties of the defect perovskites Cs<sub>2</sub>SnX<sub>6</sub> (X = Cl, Br, I). *Chinese Phys. B* **26**, 96301 (2017).
  18. Chu, Y., Hu, Y. & Xiao, Z. First-Principles Insights into the Stability Difference between ABX<sub>3</sub> Halide Perovskites and Their A<sub>2</sub>BX<sub>6</sub> Variants. *J. Phys. Chem. C* **125**, 9688–9694 (2021).
  19. Scott, S. M. *et al.* The thermal stability and consolidation of perovskite variant Cs<sub>2</sub>SnCl<sub>6</sub> using spark plasma sintering. *J. Am. Ceram. Soc.* **101**, 2060–2065 (2018).
  20. Xiao, Z. *et al.* Ligand-Hole in [SnI<sub>6</sub>] Unit and Origin of Band Gap in Photovoltaic Perovskite Variant Cs<sub>2</sub>SnI<sub>6</sub>. *Bull. Chem. Soc. Jpn.* **88**, 1250–1255 (2015).
  21. Ullah, S. *et al.* Lead-Free Cs<sub>2</sub>SnI<sub>6</sub> Perovskites for Optoelectronic Applications: Recent Developments and Perspectives. *Sol. RRL* **5**, 2000830 (2021).
  22. Wang, A. *et al.* Controlled Synthesis of Lead-Free and Stable Perovskite Derivative Cs<sub>2</sub>SnI<sub>6</sub> Nanocrystals via a Facile Hot-Injection Process. *Chem. Mater.* **28**, 8132–8140 (2016).
  23. Li, M. *et al.* Prospective on the Doping Engineering of Vacancy-Ordered Halide Double Perovskites for Enhanced Optoelectronic Properties. *J. Phys. Chem. C* (2022) doi:10.1021/acs.jpcc.2c04502.
  24. Yao, Y. *et al.* Air stable and highly efficient Bi<sup>3+</sup>-doped Cs<sub>2</sub>SnCl<sub>6</sub> for blue light-emitting diodes. *RSC Adv.* **11**, 26415–26420 (2021).

25. Das Adhikari, S. *et al.* White light emission from lead-free mixed-cation doped Cs<sub>2</sub>SnCl<sub>6</sub> nanocrystals. *Nanoscale* **14**, 1468–1479 (2022).
26. Jing, Y., Liu, Y., Zhao, J. & Xia, Z. Sb<sup>3+</sup> Doping-Induced Triplet Self-Trapped Excitons Emission in Lead-Free Cs<sub>2</sub>SnCl<sub>6</sub> Nanocrystals. *J. Phys. Chem. Lett.* **10**, 7439–7444 (2019).
27. Arfin, H. & Nag, A. Origin of Luminescence in Sb<sup>3+</sup>- and Bi<sup>3+</sup>-Doped Cs<sub>2</sub>SnCl<sub>6</sub> Perovskites: Excited State Relaxation and Spin–Orbit Coupling. *J. Phys. Chem. Lett.* **12**, 10002–10008 (2021).
28. Bounos, G. *et al.* Defect Perovskites under Pressure: Structural Evolution of Cs<sub>2</sub>SnX<sub>6</sub> (X = Cl, Br, I). *J. Phys. Chem. C* **122**, 24004–24013 (2018).
29. Jin, M. *et al.* Unraveling the triplet excited-state dynamics of Bi<sup>3+</sup> in vacancy-ordered double perovskite Cs<sub>2</sub>SnCl<sub>6</sub> nanocrystals. *Nano Res.* (2022) doi:10.1007/s12274-022-4277-7.
30. Blaha, P. *et al.* WIEN2k: An APW+lo program for calculating the properties of solids. *J. Chem. Phys.* **152**, 74101 (2020).
31. Zeng, R. *et al.* Boosting triplet self-trapped exciton emission in Te(IV)-doped Cs<sub>2</sub>SnCl<sub>6</sub> perovskite variants. *Nano Res.* **14**, 1551–1558 (2021).
32. Drummen, P. J. H., Donker, H., Smit, W. M. A. & Blasse, G. Jahn-Teller distortion in the excited state of tellurium(IV) in Cs<sub>2</sub>MCl<sub>6</sub> (M=Zr, Sn). *Chem. Phys. Lett.* **144**, 460–462 (1988).
33. Karim, M. M. S. *et al.* Anion Distribution, Structural Distortion, and Symmetry-Driven Optical Band Gap Bowing in Mixed Halide Cs<sub>2</sub>SnX<sub>6</sub> Vacancy Ordered Double Perovskites. *Chem. Mater.* **31**, 9430–9444 (2019).
34. Bala, A. & Kumar, V. Stability of the Eu<sup>2+</sup> Dopant in CsPbBr<sub>3</sub> Perovskites: A First-Principles Study. *J. Phys. Chem. C* **123**, 6965–6969 (2019).
35. Ofelt, G. S. Intensities of Crystal Spectra of Rare- Earth Ions. *J. Chem. Phys.* **37**, 511–520 (1962).
36. Xia, S. & Duan, C.-K. The simple model and its application to interpretation and assignment of 4f–5d transition spectra of rare-earth ions in solids. *J. Lumin.* **122–123**, 1–4 (2007).
37. Jia, Y., Miglio, A., Poncé, S., Mikami, M. & Gonze, X. First-principles study of the luminescence of  $\{\mathrm{Eu}\}^{\{2+\}}$ -doped phosphors. *Phys. Rev. B* **96**, 125132 (2017).

- 1
  - 2
  - 3
  - 4
  - 5
  - 6
  - 7
  - 8
  - 9
  - 10
  - 11
  - 12
  - 13
  - 14
  - 15
  - 16
  - 17
  - 18
  - 19
  - 20
  - 21
  - 22
  - 23
  - 24
  - 25
  - 26
  - 27
  - 28
  - 29
  - 30
  - 31
  - 32
  - 33
  - 34
  - 35
  - 36
  - 37
  - 38
  - 39
  - 40
  - 41
  - 42
  - 43
  - 44
  - 45
  - 46
  - 47
  - 48
  - 49
  - 50
  - 51
  - 52
  - 53
  - 54
  - 55
  - 56
  - 57
  - 58
  - 59
  - 60
  - 61
  - 62
  - 63
  - 64
  - 65
38. Baran, A. *et al.* Luminescence properties of different Eu sites in LiMgPO<sub>4</sub>:Eu<sup>2+</sup>, Eu<sup>3+</sup>. *J. Phys. Condens. Matter* **26**, 385401 (2014).
39. The rise of integrated quantum photonics. *Nat. Photonics* **14**, 265 (2020).
40. Afify, H. A. *et al.* Highly Stable Lasing from Solution-Epitaxially Grown Formamidinium-Lead-Bromide Micro-Resonators. *Adv. Opt. Mater.* **10**, 2200237 (2022).
41. Zhong, Y. *et al.* Multi-Dopant Engineering in Perovskite Cs<sub>2</sub>SnCl<sub>6</sub>: White Light Emitter and Spatially Luminescent Heterostructure. *Inorg. Chem.* **60**, 17357–17363 (2021).