



HAL
open science

Current distribution simulation for REBCO pancake coils applying low-frequency-ac current method

So Noguchi, Takanobu Mato, Seokbeom Kim

► To cite this version:

So Noguchi, Takanobu Mato, Seokbeom Kim. Current distribution simulation for REBCO pancake coils applying low-frequency-ac current method. 8th International Workshop on Numerical Modelling of High Temperature Superconductors (HTS 2022), Kévin Berger (Université de Lorraine - GREEN), Jun 2022, Nancy, France. hal-03791408

HAL Id: hal-03791408

<https://hal.science/hal-03791408v1>

Submitted on 29 Sep 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Current distribution simulation for REBCO pancake coils applying low-frequency-ac current method

So Noguchi

Grad. Sch. of Info. Sci. & Tech.
Hokkaido University
Sapporo, Japan
noguchi@ssi.ist.hokudai.ac.jp

Takanobu Mato

Grad. Sch. of Info. Sci. & Tech.
Hokkaido University
Sapporo, Japan
mato@em.ist.hokudai.ac.jp

SeokBeom Kim

Grad. Sch. of Natural Sci. & Tech.
Okayama University
Okayama, Japan
kim@ec.okayama-u.ac.jp

Abstract—In recent years, the no-insulation (NI) winding technique for rare-earth barium copper oxide (REBCO) pancake coils have been attracted in the field of high magnetic field generation. A contact resistance between turns characterize the stability of REBCO pancake coils. Hence, it is important to control the contact resistance, as well as it is necessary to measure it.

The sudden-discharging method is a popular way to measure the turn-to-turn contact resistance. It is, however, not robust against various conditions, e.g. external field, varying temperature, etc. A few years ago, we have been proposed a method to measure a contact resistance of an NI REBCO pancake coil applying a low-frequency-ac current, so called an LFAC method.

We present the validity of LFAC method through a simulation. Since the original LFAC method contains some errors, we will show a correction method together with simulation results.

Keywords—numerical simulation, REBCO magnet, turn-to-turn contact resistance

I. INTRODUCTION

The no-insulation winding technique brings great stability to rare-earth barium copper oxide (REBCO) pancake coils [1]. A key parameter of stabilization is a contact resistance between turns of NI REBCO pancake coils [2], [3]. In common, a contact resistance is measured with a sudden-discharging method [4]. Although the contact resistance varies depending on operating current, magnetic field, and temperature, the sudden-discharging method is not applicable under such varying conditions.

To overcome such difficulties, we have proposed a new measurement method applying low-frequency-ac current to an NI REBCO pancake coil [5]. Using the proposed method, so named LFAC (low-frequency-ac current) method, it was succeeded that turn-to-turn contact resistances were measured during an external field excitation or a dc current operation [6], [7]. Meanwhile, since the phase of the measured voltages differed from expected ones, the current distribution on NI REBCO pancake coil is investigated through a numerical simulation when applying the LFAC method.

II. THEORY OF LFAC METHOD

It is well known that an NI REBCO pancake coil can be simply expressed as a parallel circuit, as shown in Fig. 1 [1], [4]–[7]. When applying a sinusoidal current to an NI REBCO pancake coil, the coil impedance Z at $R_{sc} = 0$ is

$$Z = \frac{j\omega L R_{ct}}{j\omega L + R_{ct}} \quad (1)$$

where j and ω are the imaginary unit and the angular frequency, respectively. Here, taking a condition of $R_{ct} \ll \omega L$, $Z \approx R_{ct}$. That is, when ac current with high frequency carries on an NI REBCO pancake coil, the current mostly flows in the radial direction with resistance of R_{ct} . According to [5], the frequency range of 10-100 Hz is suitable for contact resistance measurement, because a current with higher frequency generates an error due to ac loss.

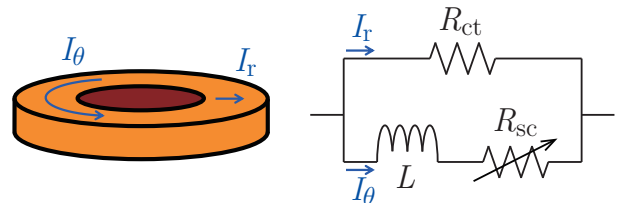


Fig. 1. NI REBCO pancake coil and its equivalent circuit model consisting of R and L in parallel. I_θ and I_r are the current in the azimuthal and radial directions, respectively. L , R_{ct} , and R_{sc} are the coil inductance, the turn-to-turn contact resistance, and the longitudinal REBCO tape resistance.

Fig. 2 shows the measured current and the voltage of NI REBCO pancake coil. Reference [6] concluded that the turn-to-turn contact resistance corresponded to V_p/I_p ($= 0.143$ m Ω), where V_p ($= 1.43$ mV) and I_p ($= 10$ A) are the peak voltage and the peak current, respectively, despite the phase difference between voltage and current ($\theta = 10.8$ deg.). The phase difference is ideally zero; however, since the phase difference of 10.8 deg. appeared, it is necessary to investigate whether it is measurement error or incompleteness of the LFAC method, with an accurate simulation. Even if the phase difference is considered, a theoretically estimated contact resistance is 0.140 m Ω ($= V_p/I_p \cos \theta$).

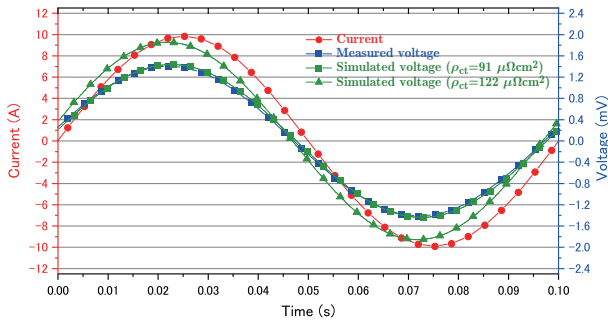


Fig. 2. Measured and simulated waveforms of voltage and current at 10 Hz.

III. PEEC SIMULATION

The current distribution is simulated with a partial element equivalent circuit (PEEC) model [8]. Table I shows the specifications of the simulated NI REBCO pancake coil [6]. The turn-to-turn contact resistance and resistivity estimated with the original LFAC method are 0.143 m Ω and 122 $\mu\Omega\cdot\text{cm}^2$, respectively.

TABLE I
NI REBCO PANCAKE COIL SPECIFICATIONS

i.d.; o.d. (mm)	60.0; 62.9
Coil height (mm)	4
Number of turns	10
Computed inductance L (μH)	12.2
Coolant	Liquid nitrogen

In the simulation, a current of 10 A, 10 Hz, which is the same condition as the experiment, is applied to the NI REBCO pancake coil. Fig. 2 also shows the simulated voltage waveform with the contact resistivity of 122 $\mu\Omega\cdot\text{cm}^2$. The simulated voltage is obviously higher than the measured one despite almost the same phase.

Fig. 3 shows the radial and azimuthal current distribution maps, where it is assumed that the same contact resistivity is uniformly distributed. At the peak of current, the current uniformly distributes in the radial direction [Fig. 3(e)]; however, the azimuthal currents remain on the innermost and outermost turns [Fig. 3(a)].

A. Correction

To fit the simulated voltage with the measured one, we investigated the value of contact resistivity. When the contact resistivity is 91 $\mu\Omega\cdot\text{cm}^2$ ($R_{ct} = 0.107$ m Ω), the waveform of simulated voltage agrees with the measured one well. The new contact resistance value is much smaller than the values estimated with LFAC method (0.143 m Ω) and theoretically derived (0.140 m Ω).

The current behaviors are more complicated than the behaviors expressed from the RL parallel circuit as shown in Fig. 1. The newly obtained contact resistance is approximately 75% of the LFAC-method one.

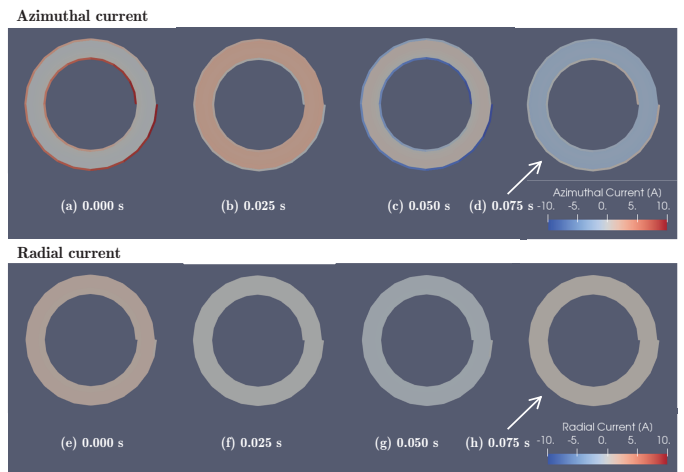


Fig. 3. Current distribution map in (a)-(d) the azimuthal and (e)-(h) the radial directions.

IV. SUMMARY

We have previously proposed the turn-to-turn contact resistance with low-frequency-ac current (LFAC). When the resistance is much smaller than the inductor impedance, the coil impedance ideally matches with the turn-to-turn contact resistance without the phase difference between current and voltage. However, the phase difference was observed in experiments, and the contact resistance was inaccurately estimated.

The current distribution is investigated using the partial element equivalent circuit (PEEC) model. It is obvious that although the current uniformly flows in the radial direction, the current azimuthally flows in the innermost and outermost turns. Using the PEEC, the contact resistance of 0.107 m Ω is newly obtained, 75% of the LFAC method.

REFERENCES

- [1] S. Hahn, D. K. Park, J. Bascuñán, and Y. Iwasa, "HTS pancake coils without turn-to-turn insulation," *IEEE Trans. Appl. Supercond.*, vol. 21, pp. 1592–1595, June 2011.
- [2] K. Katsumata, *et al.*, "Influence of the turn-to-turn contact electrical resistance on the thermal stability in meter-class no-insulation REBCO pancake coils during a local normal-state transition," *IEEE Trans. Appl. Supercond.*, vol. 27, June 2017, art. no. 4602005.
- [3] S. Noguchi, S. Hahn, A. Ishiyama, and Y. Iwasa, "A simple protection evaluation method for no-insulation REBCO pancake coils during local normal-state transition," *Supercond. Sci. and Tech.*, vol. 32, February 2019, art. no. 045001.
- [4] X. Wang, *et al.*, "Turn-to-turn contact characteristics for an equivalent circuit model of no-insulation ReBCO pancake coil," *Supercond. Sci. and Tech.*, vol. 26, January 2013, art. no. 035012.
- [5] S. Noguchi, *et al.*, "Turn-to-turn contact resistance measurement of no-insulation REBCO pancake coils," *IEEE Trans. Appl. Supercond.*, vol. 29, August 2019, art. no. 4601605.
- [6] S. Noguchi, T. Tatsuta, D. Nishikawa, H. Ueda, and S. Kim, "Turn-to-turn contact resistance measurement of no-insulation REBCO pancake coil at DC current operation," *IEEE Trans. Appl. Supercond.*, vol. 30, June 2020, art. no. 9000305.
- [7] S. Noguchi, *et al.*, "Turn-to-turn contact resistance measurement of no-insulation REBCO pancake coil: external field dependence," *IEEE Trans. Appl. Supercond.*, vol. 31, August 2021, art. no. 4602105.
- [8] T. Wang, *et al.*, "Analyses of transient behaviors of no-insulation REBCO pancake coils during sudden discharging and overcurrent," *IEEE Trans. Appl. Supercond.*, vol. 25, June 2025, art. no. 4603409.