



**HAL**  
open science

## Luminescence Enhancement Effects on Nanostructured Perovskite Thin Films for Er/Yb-Doped Solar Cells

Zhelu Hu, María Ujué González, Zhuoying Chen, Patrick Gredin, Michel Mortier, Antonio García-Martín, Lionel Aigouy

► **To cite this version:**

Zhelu Hu, María Ujué González, Zhuoying Chen, Patrick Gredin, Michel Mortier, et al.. Luminescence Enhancement Effects on Nanostructured Perovskite Thin Films for Er/Yb-Doped Solar Cells. *Nanoscale Advances*, 2022, 4 (7), pp.1786-1792. 10.1039/D1NA00782C . hal-03855910

**HAL Id: hal-03855910**

**<https://hal.science/hal-03855910>**

Submitted on 16 Nov 2022

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution - NonCommercial 4.0 International License

## ARTICLE

## Luminescence Enhancement Effects on Nanostructured Perovskite Thin Films for Er/Yb-Doped Solar Cells

Zhelu Hu,<sup>a</sup> María Ujué González,<sup>b</sup> Zhuoying Chen,<sup>a</sup> Patrick Gredin,<sup>c,d</sup> Michel Mortier,<sup>c</sup> Antonio García-Martín,<sup>b</sup> and Lionel Aigouy<sup>a†</sup>

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Recent attempts to improve solar cells performance increasing their spectral absorption interval incorporate up-converting fluorescent nanocrystals on the structure. These nanocrystals absorb low energy light and emit higher energy photons that can then be captured by the solar cell active layer. However, this process is very inefficient and it needs to be enhanced by different strategies. In this work, we have studied the effect of nanostructuring of perovskite thin films used in the fabrication of hybrid solar cells on its local optical properties. The perovskite surface was engraved with a focused ion beam to form gratings of one-dimensional grooves. We characterized the surfaces with a fluorescent scanning near-field optical microscope, and obtained maps showing a fringe pattern oriented in a direction parallel to the grooves. By scanning structures as a function of the grooves depth, ranging from 100 nm to 200 nm, we observed that a 3-fold luminescence enhancement could be obtained for the deeper ones. The near-field luminescence was found to be enhanced between the grooves, not inside them, independently of the groove depth and the incident polarization direction. This indicates that the ideal position of the nanocrystals is between the grooves. In addition, we also studied the influence of the inhomogeneities of the perovskite layer and we observed that the roughness tends to locally modify the intensity of the fringes and to distort their alignment. All the experimental results are in good agreement with numerical simulations.

### A INTRODUCTION

Thin films-based solar cells are nowadays the subject of intense research efforts due to their remarkable properties<sup>1,2</sup>. Compared to bulk materials, the small amount of matter involved in thin film fabrication makes them very competitive in terms of costs, waste and pollution, as well as the amount of energy needed to produce them. In addition, the possibility of using thin films for making flexible devices opens the way to develop new applications such as curtains, backpacks, clothes and other daily items. A recent example of thin films-based devices are hybrid halide perovskite solar cells (PSCs)<sup>3-5</sup>, which have a single-junction power conversion efficiency (PCE) above 25% and are therefore potential candidates to compete with silicon solar cells<sup>6-8</sup> due to their cost advantage in fabrication and installation. For further development to increase the efficiency of perovskite solar cells, one of the strategies is based on the optimization of optical absorption. For that,

many approaches have been proposed using micro and nanostructures able to modify the incident plane wave by scattering within the active layer or by trapping and concentrating light in high intensity near-field zones. For example, numerous dielectric materials, arranged to form photonic crystals<sup>9,10</sup>, nano-antennas<sup>11</sup>, nanoprisms,<sup>12</sup> or microlenses<sup>13</sup>, have been tested and showed an improvement of solar cells efficiency. In the case of PSCs<sup>14-17</sup>, it has also been observed that the texturization of the substrate, the electron transport layer (ETL) or directly the absorbing layer can increase the efficiency of the devices. Finally, metallic nanoparticles, which support surface plasmon resonances, can also improve the cell characteristics thanks to the enhancement of the local electromagnetic near-field<sup>18-20</sup>. In addition to increasing optical absorption, plasmonic particles can also modify the generation of excitons, enhance the charge separation, and diminish the recombination rate, thus easing the electron and hole transport in the devices<sup>21</sup>. Usually, nanostructuring is performed in order to enable light trapping and absorption in a wavelength range which is directly absorbed by the active material, typically in the visible part of the solar spectrum for PSCs. In this article, our aim is different, as we want to study the effect of a nanostructuring on the optical properties of a PSC in the near-infrared (NIR) wavelength range, which is not usually absorbed. The goal is to produce intense and localized local electromagnetic fields able to boost the up-conversion

<sup>a</sup> Laboratoire de Physique et d'Étude des Matériaux (LPEM), CNRS, ESPCI Paris, PSL Research University, UPMC, Sorbonne Universités, F-75231 Paris, France.

<sup>b</sup> Instituto de Micro y Nanotecnología IMN-CNM, CSIC, CEI UAM+CSIC, Isaac Newton 8, E-28760 Tres Cantos, Madrid, Spain.

<sup>c</sup> Institut de Recherche de Chimie Paris, Chimie ParisTech, CNRS, PSL Research University, 11 rue Pierre et Marie Curie, F-75005 Paris, France.

<sup>d</sup> Sorbonne Université, Faculté des sciences en Ingénierie, 4 place Jussieu, F-75005 Paris, France.

† [lionel.aigouy@espci.fr](mailto:lionel.aigouy@espci.fr)

luminescence of nanocrystals that would be further embedded in the absorbing layer or situated at the interface between the absorbing layer and another adjacent material (the electron or the hole transport layers, or the metallic contact for instance)<sup>22-24</sup>. The principle of this effect is straightforward. Some rare-earth cations like  $\text{Er}^{3+}$  can absorb the NIR photons unabsorbed by PSCs and reemit it by luminescence in the visible range, at wavelengths which can be harvested is absorbed by PSCs. However, this effect is rather weak compared to the fluorescence in organic molecules or semiconducting quantum dots since it depends on a two and/or three-photon absorption process whose cross-section efficiency is low<sup>25,26</sup>. Boosting the up-conversion absorption process and the emitted luminescence can be done with plasmonic<sup>22,23,25,27-30</sup> or dielectric nanoparticles<sup>29-31</sup>. In the case of metallic nanoparticles, the luminescence enhancement arises either from an increase of the local electromagnetic field<sup>22,32,33</sup> due to plasmonic resonances, or from an increase of the decay rate<sup>34-37</sup>. In the case of dielectric micro- and nano-structures, on the other hand, incident light can be trapped and concentrated in different zones due to the refractive index contrast between the structures and the environment. Mie resonances, due to the local charges and displacement currents induced by the incident wave, can also produce strong electromagnetic fields both inside and outside the particles<sup>37</sup>.

The use of top-down lithography techniques to obtain micro- and nano-structuration in perovskite-based devices has consolidated in the last years<sup>38-39</sup>, and in particular, direct patterning by means of focused ion beam (FIB) has already been demonstrated to be a technology compatible with these materials<sup>40,41</sup>. Here, we have employed FIB to engrave grooves arrays on perovskite thin films. As a proof-of-concept, we will

show that these grooves can generate strong variations of the local electromagnetic field and induce large up-conversion luminescence enhancements compared to a flat surface. The enhancement depends on the dimensions of the structure (width, depth and period) and on the polarization direction of the incident light. We paid particular attention to the influence of the grooves depth, which is a parameter that strongly influences the contrast and the luminescence enhancement. We will also show that the presence of roughness and defects generate fluctuations and hot spots that modify the luminescence. Although the structures have been fabricated on a sub-millimeter scale, they can also be created on much larger scales using, for instance, interference lithography or soft lithography<sup>42,43</sup>.

## B TECHNIQUES AND METHODS

**A Perovskite deposition.** Fluorine-doped tin oxide ( $\text{SnO}_2:\text{F}$  or FTO) coated  $\text{SiO}_2$  substrates (FTO thickness = 500 nm) were cleaned by four successive ultrasonication baths with soap (2% Hellmanex in water), deionized water, acetone and isopropanol, for 15 min each. Then the dried FTO substrates were treated by an oxygen plasma process during 10 min. A thin (50 nm) compact layer of  $\text{TiO}_2$  (cp- $\text{TiO}_2$ ) was prepared according to the recipe given in ref 44. Briefly, a drop of a sol-gel precursor solution of titanium (IV) isopropoxide was spun at 4000 rpm for 25 s onto FTO substrates. The samples were annealed in an oven in air first at 120 °C for 15 min and then at 450 °C for 60 min. After cooling down to room temperature, the substrates were transferred to an Ar-filled glovebox to prepare the perovskite absorber layer. In the following descriptions, the compounds formamidinium and methylammonium will be referred as FA and MA respectively. The mixed cation perovskite  $\text{Cs}_{0.05}(\text{FA}_{0.83}\text{MA}_{0.17})_{0.95}\text{Pb}(\text{I}_{0.83}\text{Br}_{0.17})_3$  precursor solution was synthesized by dissolving FAI (1 M), MABr (0.2 M),  $\text{PbI}_2$  (1.1 M), and  $\text{PbBr}_2$  (0.2 M) in a solvent mixture of anhydrous dimethylformamide (DMF) and dimethyl sulfoxide (DMSO) (4:1, v/v) according to previous reports<sup>17</sup>. In parallel, a stock solution containing 1.5 M of CsI dissolved in DMSO was added into the above-mentioned precursor solution to achieve the desired composition<sup>45</sup>. The perovskite precursor solution was spin-coated onto the cp- $\text{TiO}_2$  surface performed by a consecutive two-step process first at 1000 rpm for 10 s and then at 5000 rpm for 45 s. During the second spin-coating step, 100  $\mu\text{l}$  chlorobenzene was dropped on the spinning substrate after 30 s of spinning. After spin-coating, the substrates with perovskite film were annealed at 100 °C for 60 min on a hot-plate. The thickness of the obtained perovskite film was 500 nm. The structure of the sample is illustrated in Fig. 1(a).

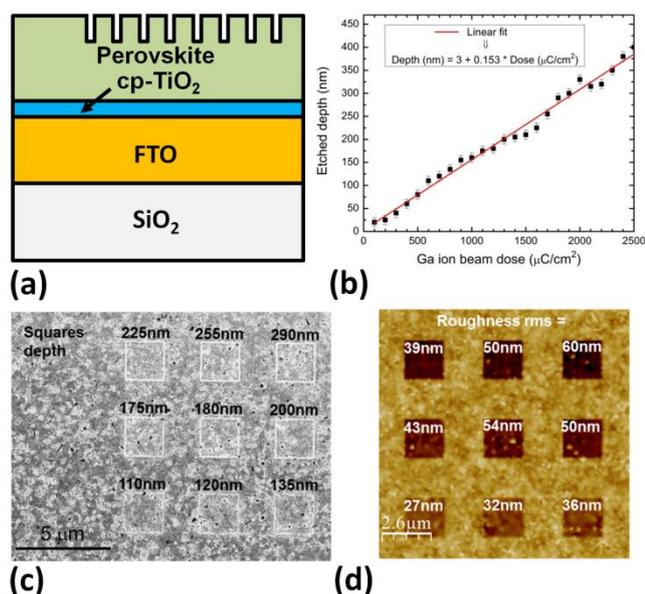


Figure 1: (a) Structure of the patterned perovskite thin film; (b) influence of the Ga ions dose on the etching depth; (c) SEM picture of the perovskite surface with etched squared motives of different depths. The depths are indicated on top of each square. (d) AFM image of the same zone than (c) with corresponding rms roughness values.

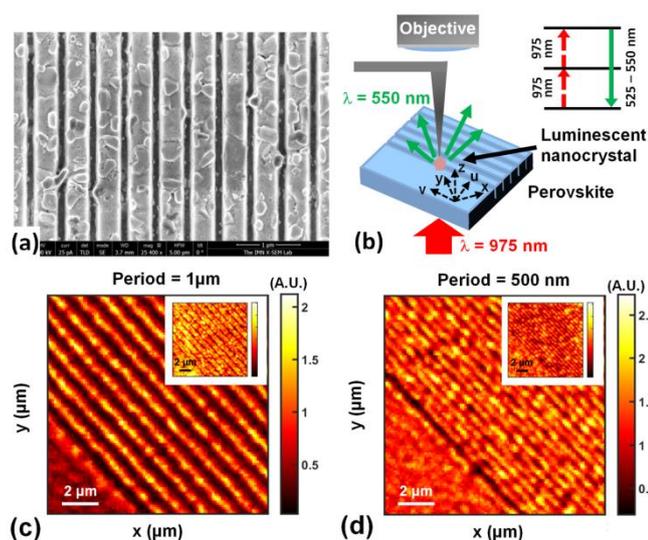


Figure 2: (a) SEM picture of a 500 nm period grating with 150 nm wide grooves milled in the perovskite surface; (b) sketch of the experimental configuration for near-field measurements; (c) luminescence image obtained on a structure with  $p = 1 \mu\text{m}$ ,  $d = 200 \text{ nm}$  and  $w = 250 \text{ nm}$ . Light polarization is parallel to the grooves; (d) same than (c) but with  $p = 500 \text{ nm}$ . The insets are the corresponding AFM images simultaneously acquired during scanning (color scale: 0 - 300nm).

**B FIB nano-fabrication process.** The sample was then introduced into the chamber of a focused ion beam system (Raith ionLINE), equipped with a Ga ions source. Milling was performed with a Ga<sup>+</sup> beam accelerated at 30 kV, ion current of 44 pA, a fixed beam step size of 6 nm and 50 ion scans (loops) for each structure. To calibrate the milling rate of the perovskite film, squared motives were created and characterized by atomic force microscopy (AFM). We show in Fig. 1(b) the influence of the Ga ions dose on the etched depth. A linear relationship was measured, enabling to adjust the depth with the dose in future fabrication runs. The surface appearance and roughness created by the FIB milling on the perovskite film was characterized by scanning electron microscopy (SEM) and AFM. As shown on the SEM picture in Fig. 1(c), the perovskite surface looks identical between etched and un-etched zones, with alternative white and dark grains, as usually observed on this material<sup>4</sup>. The rms roughness, measured by AFM, is indicated on Fig. 1(d) for the squares shown in Fig. 1(c), where the depth of each motive is also written on its top. It varies between 27 nm to 60 nm and is of the same order of magnitude as that on the un-etched zones (around 30 nm).

In this study, we chose to analyze arrays of one-dimensional (1D) structures made of grooves with a period,  $p$ , equal to 500 nm and 1  $\mu\text{m}$ . Each array had a size of 50 x 50  $\mu\text{m}^2$ , in such a way that several patterns with different parameters could be fabricated on the same sample. We show in Fig. 2(a) a SEM picture of an array with a period equal to 500 nm, and a groove width ( $w$ ) and depth ( $d$ ) equal to 150 nm and 380 nm, respectively. Although some grains, which are probably residues from the erosion process, remain on the surface, the

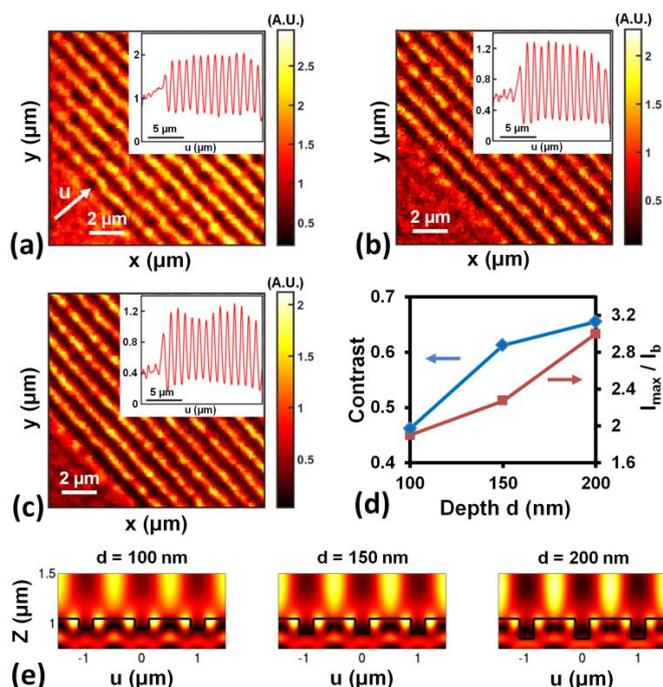


Figure 3: (a), (b) and (c) Luminescence images (the polarization of the impinging wave is parallel to the grooves) measured by scanning the structures with  $p = 1 \mu\text{m}$ ,  $w = 250 \text{ nm}$  and  $d = 100 \text{ nm}$  (a),  $d = 150 \text{ nm}$  (b), and  $d = 200 \text{ nm}$  (c). The insets are cross sections extracted from the images in a direction perpendicular to the grooves ( $u$ ); (d) measured contrast and intensity ratio as a function of the depth; (e) FDTD calculation of the near-field intensity for the three structures. The maps are cuts in a plane perpendicular to the surface and to the grooves ( $uz$ -plane). Light polarization is again parallel to the grooves.

grooves are regularly spaced with abrupt edges confirming that the direct milling of a perovskite material with a FIB can be performed in a well-controlled and non-destructive way.

**C Near-field measurement technique.** In order to measure the localization of the electromagnetic field and to evaluate the luminescence enhancement, we used a homemade scanning near-field optical microscope (SNOM) whose probe is a fluorescent nanocrystal. This nanocrystal is made of  $\text{KY}_3\text{F}_{10}$  codoped with  $\text{Er}^{3+}$  (2 mole %) and  $\text{Yb}^{3+}$  (8 mole %) ions and is glued at the end of a sharp AFM tip<sup>31,33</sup>. The nanocrystal synthesis is described in the electronic supplementary informations file. The diameter of the nanocrystal used in this study was between 50 nm and 200 nm. The principle of the experiment is described in Fig. 2(b), which also contains the definition of direction axis. The sample is set on a scanning stage and illuminated in a transmission mode with an internally modulated laser beam ( $\lambda_{\text{exc}} = 975 \text{ nm}$ ,  $f_{\text{mod}} = 320 \text{ Hz}$ ,  $P_{\text{peak}} = 30 \text{ mW}$ ) focused on a  $\sim 50 \mu\text{m}$  wide spot. The tip scans the sample in the tapping mode and the nanocrystal is excited at  $\lambda_{\text{exc}}$  by the electromagnetic field localized on the surface. After the absorption of two photons, it emits light by luminescence in the 525 - 550 nm range. A simplified energy band diagram of the up-conversion excitation is shown in the inset of Fig. 2(b). A more detailed energy band diagram and a

luminescence spectrum are shown in the electronic supplementary information file. The emitted light is collected with a large numerical aperture objective (N.A. = 0.8) and is sent to a photomultiplier tube connected to a lock-in amplifier. The images are recorded with a homemade Labview program that also drives the movement of the scanning stage.

**D Simulation methods.** A finite difference time domain (FDTD) method has been used to calculate the near-field intensity with a proprietary code Lumerical®, which provides us with a robust and reliable solver for Maxwell's equations. We use an impinging plane wave from the substrate side, of unit amplitude everywhere. In the simulation region we employ periodic boundary conditions using as unit cell a span of 5 trenches in the plane ( $x$  and  $y$  directions) and perfect absorbing layers in the vertical ( $z$ -direction) that spans  $10\ \mu\text{m}$ . The refractive index of the perovskite material used was  $n = 2.32$  at  $975\ \text{nm}$  wavelength as measured in ref. 46 by ellipsometry on a similar compound. The refractive indexes for the rest of involved materials are:  $\text{SiO}_2 = 1.45$ ;  $\text{FTO} = 1.43$ ,  $\text{TiO}_2 = 2$ . Technical parameters are: mesh size  $5\ \text{nm}$  in the  $xy$ -plane for the whole simulation, in  $z$  it is varied from  $5\ \text{nm}$  in the trenched area, to  $25\ \text{nm}$  deep in the air and substrate. The pulse duration has been set to  $1\ \text{ps}$ , more than enough to ensure that all radiation has exited the simulation region. Under these conditions the total field is computed to give rise to the near field intensity color plots. All fields are normalized

to the intensity of the impinging plane wave.

## C RESULTS AND DISCUSSION

We show in Fig. 2(c) and 2(d) two luminescence images obtained on structures having a period of  $1\ \mu\text{m}$  and  $500\ \text{nm}$ , respectively. The corresponding AFM images are shown in the insets (axes are defined in Fig. 2(b)). A portion of unstructured perovskite surface is visible on the lower left part of the images. The polarization of the incident laser beam was parallel to the grooves. As we can see, the presence of the grooves creates bright and dark lines, oriented in a direction parallel to the grooves. Although the measured quantity is the nanocrystal luminescence, we recently observed on other structures<sup>31,33</sup> that it is directly linked to the intensity of the near-field on the surface at the excitation wavelength. The observed light contrast lines are due to the refractive index difference between the air and the perovskite ( $n = 2.32$ ), which perturbs the incident plane wave and tends to confine the light in some particular zones. They result from the combination of the zero order diffraction and other modes in the perovskite layer that are evanescent in the vertical  $z$ -direction. These periodic structures constitute then a ridge waveguide grating directly engraved in the perovskite. Among the different geometrical parameters that influence the intensity of the electromagnetic field and the luminescence, we decided to analyze in more detail the effect of the groove depth on the contrast.

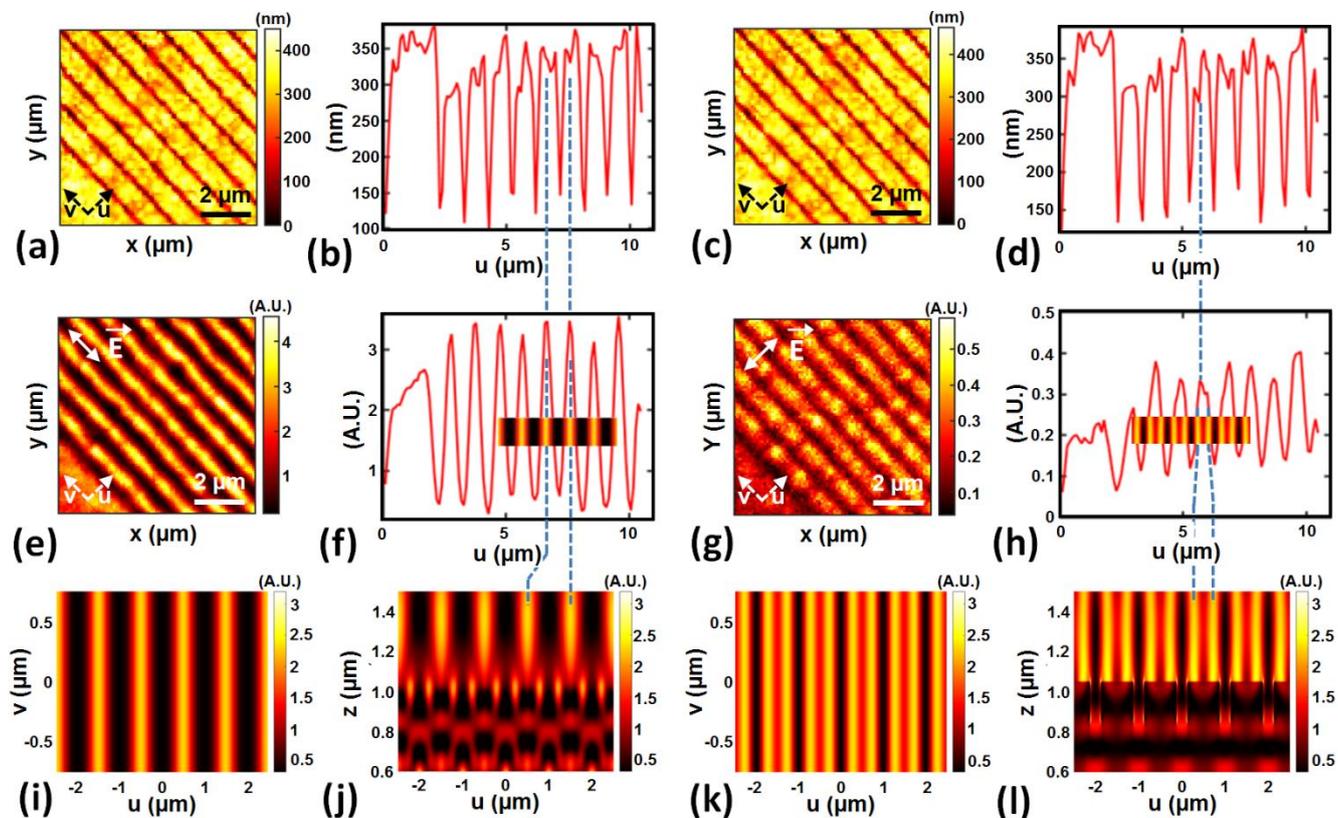


Figure 4: Topography (a,b,c,d) and luminescence (e,f,g,h) measured by scanning the array with period  $p = 1\ \mu\text{m}$  and grooves size  $w = 250\ \text{nm}$  and  $d = 200\ \text{nm}$ ; (b,d,f,h) are cross-sections extracted from images (a,c,e,g). FDTD maps (i,j,k,l) of the electromagnetic near-field intensity calculated in the  $uv$ -plane parallel to the surface (i,k), and in the  $uz$ -plane perpendicular to both surface and grooves (j,l) for the same array. The light polarization is either parallel (e,f,i,j) or perpendicular (g,h,k,l) to the grooves.

We therefore characterized three structures having the same period ( $p = 1 \mu\text{m}$ ), the same groove width ( $w = 250 \text{ nm}$ ) and three groove depths ( $d = 100 \text{ nm}$ ,  $d = 150 \text{ nm}$ , and  $d = 200 \text{ nm}$ ). The incident polarization was parallel to the grooves. The luminescence images are displayed in Fig. 3 and luminescence intensity cross-sections in the direction perpendicular to the grooves are shown in the insets. The oscillatory behavior is huge and presents highly contrasted fringes. If we compare the maximum intensity of the fringes  $I_{\text{max}}$  to the intensity on the unstructured surface  $I_b$ , we find that the ratio  $I_{\text{max}} / I_b$  increases from 2 to 3 when the groove depth increases from 100 nm to 200 nm [Fig. 3(d)]. Similarly, the contrast, defined as  $(I_{\text{max}} - I_{\text{min}}) / (I_{\text{max}} + I_{\text{min}})$  where  $I_{\text{min}}$  is the minimum fringes intensity, also plotted in Fig. 3(d) as a function of the depth, augments from 0.45 to 0.65. So, both the intensity and the contrast increase with the groove depth. To confirm the measured results, FDTD simulations, showing the variations of the near-field intensity with  $d$ , are depicted in Fig. 3(e). The maps are cuts in the plane perpendicular to the surface and to the grooves ( $uz$ -plane). As we can see, the oscillatory behavior is very similar to the one of the experiments, and the contrast also increases as the depth increases (as it is confirmed by the increasing intensity of the bright lines appearing in the simulation plots). From the cross-sections, we see that the bright lines are located between the grooves whereas the minimum is located above them. This result can also be extracted from a careful comparison between luminescence and topographic experimental data, see Figs. 2(c-d), and it will be confirmed later (Fig. 4). In the simulation, two bright spots of less intensity are also visible on the sides of the grooves but they do not appear on the luminescence images, probably because of the lack of resolution of the fluorescent nanocrystal used in the measurements and also because they are mainly located inside the perovskite material. These experiments and the simulation indicate that the maximum luminescence enhancement takes place between the grooves.

All the previous images were measured with an illumination whose polarization was parallel to the grooves. We next studied the influence of the polarization direction on the luminescence enhancement. We focused on the sample with the larger contrast ( $p = 1 \mu\text{m}$ ,  $w = 250 \text{ nm}$ , and  $d = 200 \text{ nm}$ ) and compared the images obtained with both parallel and perpendicular polarizations [see Figs. 4(e) and 4(g)]. We cannot compare the relative intensities of the two images because the excitation intensity is different for each situation; however, it appears that the contrast is better in the case of the parallel polarization than for the perpendicular one. Moreover, the bright line is broader in the case of the perpendicular polarization. To understand this broadening, we calculated by FDTD the near-field intensity on this structure for both polarizations [see Figs. 4(i), 4(j), 4(k) and 4(l)]. In the case of the perpendicular polarization, the simulation reveals that the near-field is in fact composed of two peaks located on both sides of the grooves. These two peaks are not clearly contrasted, the intensity dropping only by  $\sim 30\%$  between them [Figs. 4(k) and 4(l)]. In the experimental image, on the other hand, these two peaks are merged in a single one. The

reasons that can explain this are: i) an eventual lack of resolution induced by the fluorescent nanocrystal glued at the tip end due to its size, and ii) some roughness and residues that can enlarge the near-field distribution, thus impeding the separation and merging the two fringes. These two explanations are both credible and explain why we only see a single but broader peak. Moreover, by aligning and comparing the cross-sections taken along the direction perpendicular to the grooves ( $u$ -axis) in both experimental topography and luminescence images [Figs. 4(b), 4(d), 4(f) and 4(h)], as well as the FDTD maps, it can be seen that, independently of the polarization, the observed luminescence enhancement is located between the grooves. Considering the application we

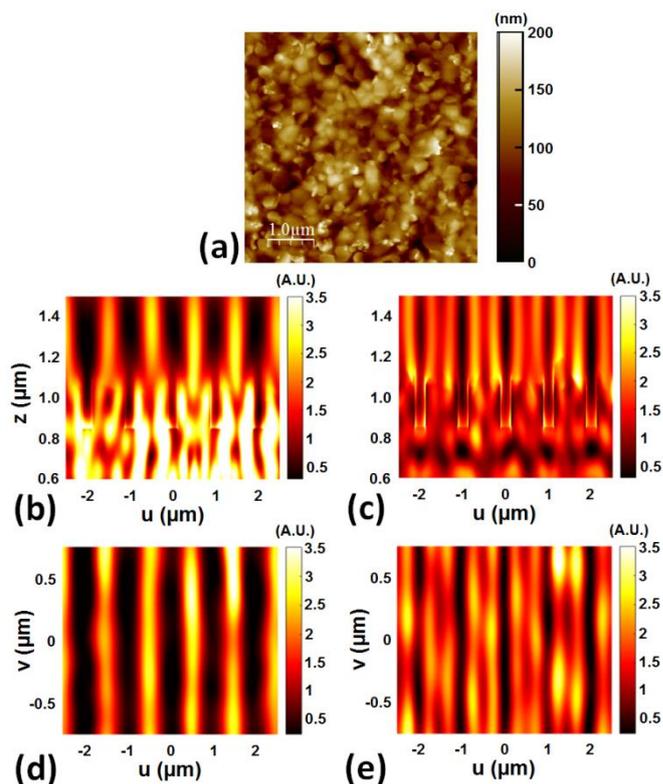


Figure 5: AFM image of the topography of the perovskite surface (a); calculated FDTD maps of the near-field intensity for a groove array ( $p = 1 \mu\text{m}$ ,  $w = 250 \text{ nm}$  and  $d = 200 \text{ nm}$ ) incorporating roughness in the  $uz$ -plane for parallel (b) and perpendicular (c) incident light polarizations, and in the  $uv$ -plane for parallel (d) and perpendicular (e) polarizations.

described in the introduction, i.e. the incorporation of fluorescent up-converting nanocrystals inside the nanostructured solar cell, illuminated by an unpolarized solar radiation, this experiment indicates that the nanocrystals have to be placed at this exact location, between the grooves.

From the luminescence maps shown in Fig. 2, 3, and 4, we see that the bright lines are not perfectly lined up and that they are not of constant intensity. This may be due to some residues left from the milling but also to the roughness of the perovskite surface. Following this idea, we next tried to evaluate the effect of roughness on the near-field distribution on the surface. For that, we performed new FDTD calculations where we introduced some roughness in the perovskite surface using a built-in Lumerical® function for a random

interface. We used a rms value of 40 nm and a correlation length of 200 nm, to resemble the grain size and height fluctuations observed experimentally (see AFM image in Fig. 5(a), where a nominal roughness of 30 nm was obtained, with grain sizes ranging between 50 and 400 nm). The results for an array of grooves with  $p = 1 \mu\text{m}$ ,  $w = 250 \text{ nm}$  and  $d = 200 \text{ nm}$  are shown in Fig. 5(b-e), where intensity near-field maps taking into account the roughness are depicted along  $uz$ - and  $uv$ -planes for both light polarization directions. Compared to the FDTD maps without roughness shown for instance in Figs. 4(i), 4(j), 4(k) and 4(l), both the intensity and the shape are modified from fringe to fringe. The intensity can be locally enhanced and forms hot spots where luminescence is increased. In the case of the perpendicular polarization [Figs. 5(c) and 5(e)], we can see that the roughness tends to enlarge the fringes and merge them. Combined to the space-averaging due to the size of the fluorescent nanocrystal, it is not surprising that we were not able to separate the two fringes in the luminescence experiments [see Figs. 4(g) and 4(h)]. The effect of roughness is less important in the case of parallel polarization for which the fringes are more separated and contrasted [Figs. 5(b) and 5(d)]. As measured experimentally [see Fig. 4(f)], the full width at half maximum of the fringes for this polarization is approximately 400 nm, in agreement with the FDTD simulations shown in Fig. 4(i) and Fig. 5(d). This means that the luminescence enhancement, compared to the unstructured perovskite surface, occurs in this entire large zone. For our application, this situation is very interesting because this area is wide enough to be easily covered with a large amount of fluorescent nanocrystals, thus contributing effectively to the improvement of the solar cell efficiency by increasing the absorption of infrared radiation and its re-emission in the visible range.

Another positive effect that could have both the nanostructuring and the presence of fluorescent nanocrystals is the improved scattering and trapping of visible light inside the perovskite layer. This could result in an enhanced absorption of the visible range of the solar spectra compared to the flat surface. We did not make this study here, keeping focused on the near-field effects in the NIR, but it could be interesting to couple the effect of the nanostructuring in these two spectral zones (absorbed visible light and unabsorbed NIR) and optimize the structures to maximize both of them. On the other hand, many questions could be raised on the negative effects that could have the nanocrystals on the electrical properties of the solar cells. If we refer to recent studies, it has been reported that the incorporation of plasmonic<sup>20,21</sup> or dielectric<sup>47</sup> nanoparticles improved the PCE of the devices, thus we are therefore confident that fluorescent nanocrystals would have a very limited negative effect. Finally, in this study, we only varied the depth of the grooves, but a deeper optimization of their width as well as of the period of the array could be done by FDTD and would probably contribute to design structures that provide larger luminescence enhancements.

## Conclusions

We fabricated perovskite thin films used in hybrid solar cells and engraved their surface with a focused ion beam. Our aim was to create zones where infrared light is both localized and enhanced to boost the luminescence of up-converting nanocrystals placed on the material. We created arrays of grooves of variable depth and we studied them by near-field luminescence microscopy. We observed periodic luminescence variations and the formation of fringes oriented in the direction parallel to the grooves. A luminescence enhancement by a factor of 2 to 3 was measured when the nanocrystals are situated between the grooves compared to the unstructured perovskite surface. We found that the enhancement and the intensity contrast were both larger when increasing the groove depth. The polarization of the incident light has also an effect on the electromagnetic field distribution. Either a single or two fringes appear when the incident polarization is parallel or perpendicular to the grooves, respectively. All the experimental results are in good agreement with numerical calculations performed by FDTD. The influence of the inhomogeneities of the perovskite layer was also studied and showed that the roughness tends to locally modify the intensity of the fringes and to distort their alignment. The measurements and simulations indicate that they can lead to additional hot spots. From our study, we showed that, for unpolarized radiation, which is the operating situation of solar cells under sunlight, the ideal position of the nanocrystals is between the grooves, where luminescence can be enhanced. As a prospect, further optimization could be made by changing the period and the width of the grooves and by improving the quality of the surface to reduce the roughness. The design of two-dimensional structures like squares or circular disks could also lead to larger enhancements, and the structures would in that case be insensitive to polarization effects.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors thank the support from the DIM Nano-K program from "Région Ile de France", from the Idex Paris Sciences & Lettres through the grant ANR-10-IDEX-0001-02 PSL, from the CNRS and the CSIC through the Spanish-French program PICS (grant SolarNano #PICS07687 and #PIC2016FR2), and the PROCES project (ANR-17-CE05-0028-01). They also acknowledge the service from the MiNa Laboratory at IMN, which is funded from CM (project S2018/NMT-4291 TEC2SPACE), MINECO (project CSIC13-4E-1794) and EU (FEDER, FSE).

## Footnotes

††The nanocrystal fabrication procedure, the characterization, and the near-field tip fabrication procedure have been described in the ESI data file.

## References

- 1 T. D. Lee and A. U. Ebong, *Renew. Sust. Energ. Rev.* **2017**, *70*, 1286.
- 2 M. Powalla, S. Paetel, E. Ahlswede, R. Wuerz, C. D. Wessendorf, and T. Magorian Friedlmeier, *Appl. Phys. Rev.* **2018**, *5*, 041602.
- 3 M. Liu, M. B. Johnston and H. J. Snaith, *Nature* **2013**, 501, 395.
- 4 H. Zhou, Q. Chen, G. Li, S. Luo, T.-B. Song, H.-S. Duan, Z. Hong, J. You, Y. Liu, Y. Yang, *Science* **2014**, 345, 542.
- 5 J. H. Heo, S. H. Im, J. H. Noh, T. N. Mandal, C. S. Lim, J. A. Chang, Y. H. Lee, H. J. Kim, A. Sarkar, M. K. Nazeeruddin, M. Grätzel and S. Il Seok, *Nat. Photonics* **2013**, *7*, 486.
- 6 W. S. Yang, J.H. Noh, N. J. Jeon, Y. C. Kim, S. Ryu, J. Seo, S. Il Seok, *Science* **2015**, 348, 1234.
- 7 Q. Jiang, L. Zhang, H. Wang, X. Yang, J. Meng, H. Liu, Z. Yin, J. Wu, X. Zhang, J. You, *Nat. Energy* **2017**, *2*, 16177.
- 8 Woon Seok Yang, Byung-Wook Park, Eui Hyuk Jung, Nam Joong Jeon, Young Chan Kim, Dong Uk Lee, Seong Sik Shin, Jangwon Seo, Eun Kyu Kim, Jun Hong Noh, Sang Il Seok, *Science* **2017**, 356, 1376.
- 9 P. Bermel, C. Luo, L. Zeng, L. C. Kimerling, and J. D. Joannopoulos, *Opt. Express* **2007**, *15*, 16986.
- 10 S. B. Mallick, M. Agrawal, and P. Peumans, *Opt. Express* **2010**, *18*, 5691, (2010).
- 11 Y. Yu, V.E. Ferry, P. Alivisatos, L. Cao, *Nano Lett.* **2012**, *127*, 3674.
- 12 D.-L. Wang, H.-J. Cui, G.-J. Hou, Z.-G. Zhu, Q.-B. Yan and G. Su, *Sci. Rep.* **2016**, *6*, 18922.
- 13 A. Peer, R. Biswas, J.-M. Park, R. Shinar and J. Shinar, *Opt. Express* **2017**, *25*, 10704.
- 14 L. Zheng, Y. Ma, S. Chu, S. Wang, B. Qu, L. Xiao, Z. Chen, Q. Gong, Z. Wu and X. Hou, *Nanoscale* **2014**, *6*, 8171.
- 15 A. R. Pascoe, S. Meyer, W. Huang, W. Li, I. Benesperi, N. W. Duffy, L. Spiccia, U. Bach and Y.-B. Cheng, *Adv. Funct. Mater.* **2016**, *26*, 1278.
- 16 M. Jošt, S. Albrecht, L. Kegelmann, C. M. Wolff, F. Lang, B. Lipovšek, J. Krč, L. Korte, D. Neher, B. Rech and M. Topič, *ACS Photonics* **2017**, *4*, 1232.
- 17 Z. Hu, J. García-Martín, Y. Li, L. Billot, B. Sun, F. Fresno, A. García-Martín, M. U. González, L. Aigouy, and Z. Chen, *ACS Appl. Mater. Interfaces* **2020**, *12*, 5979.
- 18 M. E. Ferry, L. A. Sweatlock, D. Pacifici, and H. A. Atwater, *Nano Lett.* **2008**, *8*, 4391.
- 19 H. A. Atwater and A. Polman, *Nature Mater.* **2010**, *9*, 205.
- 20 R. T. Ginting, S. Kaur, D.-K. Lim, J.-M. Kim, J. H. Lee, S. H. Lee and J.-W. Kang, *ACS Appl. Mater. Interfaces* **2017**, *9*, 36111.
- 21 Q. Luo, C. Zhang, X. Deng, H. Zhu, Z. Li, Z. Wang, X. Chen and S. Huang, *ACS Appl. Mater. Interfaces* **2017**, *9*, 34821.
- 22 D. M. Wu, A. Garcia-Etxarri, A. Salleo, J.A. Dionne, *J. Phys. Chem. Lett.* **2014**, *5*, 4020.
- 23 P. Wang, Z. Li, W.J. Salcedo, Z. Sun, S. Huang, A.G. Brolo, *Physical Chemistry Chemical Physics* **2015**, *17*, 16170.
- 24 M. Schoenauer Sebag, Z. Hu, K. de Oliveira Lima, H. Xiang, P. Gredin, M. Mortier, L. Billot, L. Aigouy and Z. Chen, *ACS Appl. Energy Mater* **2018**, *18*, 3537.
- 25 Y.-L. Wang, N. M. Estakhri, A. Johnson, H.-Y. Li, L.-X. Xu, Z. Zhang, A. Alù, Q.-Q. Wang and C.-K. Shih, *Sci. Rep.* **2015**, *5*, 10196.
- 26 J.-C. Boyer and F. C. J. M. Van Veggel, *Nanoscale* **2010**, *2*, 1417.
- 27 J. He, W. Zheng, F. Ligmajer, C.-F. Chan, Z. Bao, K.-L. Wong, X. Chen, J. Hao, J. Dai, S.-F. Yu and D. Y. Lei, *Light: Science & Applications* **2017**, *6*, 16217.
- 28 D. Zhou, D. Liu, W. Xu, Z. Yin, X. Chen, P. Zhou, S. Cui, Z. Chen and H. Song, *ACS Nano* **2016**, *10*, 5169.
- 29 Z. Yin, H. Li, W. Xu, S. Cui, D. Zhou, X. Chen, Y. Zhu, G. Qin and H. Song, *Adv. Mater.* **2016**, *28*, 2518.
- 30 S. Han, R. Deng, X. Xie and X. Liu, *Angew. Chem. Int. Ed.* **2014**, *53*, 11702.
- 31 H.-J. Lin, K. de Oliveira Lima, P. Gredin, M. Mortier, L. Billot, Z. Chen and L. Aigouy, *Appl. Phys. Lett.* **2017**, *111*, 251109.
- 32 J. C. Goldschmidt and S. Fischer, *Adv. Opt. Mat.* **2015**, *3*, 510.
- 33 L. Aigouy, M.-U. González, H.-J. Lin, M. Schoenauer-Sebag, L. Billot, P. Gredin, M. Mortier, Z. Chen, and A. García-Martín, *Nanoscale* **2019**, *11*, 10365.
- 34 P. Anger, P. Bharadwaj and L. Novotny, *Phys. Rev. Lett.* **2006**, *96*, 113003.
- 35 S. Kühn, U. Håkanson, L. Rogobete and V. Sandoghdar, *Phys. Rev. Lett.* **2006**, *97*, 017402.
- 36 S. Fischer, D. Kumar, F. Hallermann, G. V. Plessen and J. C. Goldschmidt, *Opt. Exp.* **2016**, *24*, 460.
- 37 P. Albella, M. A. Poyli, M. K. Schmidt, S. A. Maier, F. Moreno, J. J. Saenz, and J. Aizpurua, *J. Phys. Chem. C* **2013**, *117*, 13573.
- 38 B. Jeong, H. Han, and C. Park, *Adv. Mater.* **2020**, *32*, 2000597.
- 39 J. Harwell, J. Burch, A. Fikouras, M. C. Gather, A. Di Falco, and I. D. W. Samuel, *ACS Nano* **2019**, *13*, 3823.
- 40 M. S. Alias, Y. Yang, T. K. Ng, I. Dursun, D. Shi, M. I. Saidaminov, D. Priante, O. M. Bakr, and B. S. Ooi, *J. Phys. Chem. Lett.* **2016**, *7*, 137.
- 41 Y. Wang, Z. Gu, Y. Ren, Z. Wang, B. Yao, Z. Dong, G. Adamo, H. Zeng, and H. Sun, *ACS Appl. Mater. Interfaces* **2019**, *11*, 15756.
- 42 K. Wang, G. Xing, Q. Song, and S. Xiao, *Adv. Mater.* **2021**, *33*, 2000306.
- 43 A. Kessel, C. Frydendahl, S. R. K. C. Indukuri, N. Mazurski, P. Arora, and U. Levy, *Adv. Opt. Mater.* **2020**, *8*, 2001627.
- 44 E. Edri, S. Kirmayer, D. Cahen and G. Hodes, *J. Phys. Chem. Lett.* **2013**, *4*, 897.
- 45 M. Saliba, T. Matsui, J.-Y. Seo, K. Domanski, J.-P. Correa-Baena, M. Khaja Nazeeruddin, S. M. Zakeeruddin, W. Tress, A. Abate, A. Hagfeldt and M. Grätzel, *Energy Environ. Sci.* **2016**, *9*, 1989.
- 46 Laurie J. Phillips, Atef M. Rashed, Robert E. Treharne, James Kay, Peter Yates, Ivona Z. Mitrovic, Ayendra Weerakkody, Steve Hall, Ken Durose, *Solar Energy Materials & Solar Cells* **2016**, *147*, 327.
- 47 Chenxi Zhang Zaifeng Li, Xueshuang Deng, Bing Yan, Zengbo Wang, Xiaohong Chen, Zhuo Sun, Sumei Huang, *Solar Energy* **2019**, *188*, 839.