



**HAL**  
open science

## Transparent materials based on semiconducting ZnO: glass-ceramics and optical ceramics doped with rare-earth and transition-metal ions

Olga Dymshits, Elena Gorokhova, Irina Alekseeva, Valery Golubkov, Michael Shepilov, Alexander Khubetsov, Marina Tsenter, Daria Shemchuk, Anastasiya Bachina, Anna Volokitina, et al.

### ► To cite this version:

Olga Dymshits, Elena Gorokhova, Irina Alekseeva, Valery Golubkov, Michael Shepilov, et al.. Transparent materials based on semiconducting ZnO: glass-ceramics and optical ceramics doped with rare-earth and transition-metal ions. *Journal of Non-Crystalline Solids*, 2022, 588, pp.121625. 10.1016/j.jnoncrysol.2022.121625 . hal-03858730

**HAL Id: hal-03858730**

**<https://hal.science/hal-03858730>**

Submitted on 18 Nov 2022

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Transparent materials based on semiconducting ZnO: glass-ceramics and optical ceramics doped with rare-earth and transition-metal ions

Olga Dymshits<sup>1</sup>, Elena Gorokhova<sup>1</sup>, Irina Alekseeva<sup>1</sup>, Alexander Khubetsov<sup>1</sup>, Daria Shemchuk<sup>1</sup>, Valery Golubkov<sup>2</sup>, Michael Shepilov<sup>1</sup>, Inastasiya Bachina<sup>1</sup>, Anna Volokitina<sup>3</sup>, Lisa Basyrova<sup>4</sup>, Michail Baranov<sup>3</sup>, Eugenia Oreschenko<sup>1</sup>, Xavier Mateos<sup>5,6</sup>, Pavel Loiko<sup>4</sup>, Aleksandr Zhilin<sup>7</sup>

<sup>1</sup> *S.I. Vavilov State Optical Institute, 36 Babushkina St., 192171 St.*

*Petersburg, Russia*

<sup>2</sup> *Institute of Silicate Chemistry of Russian Academy of Sciences, Adm. Makarova emb., 2, St. Petersburg, 199034, Russia*

<sup>3</sup> *ITMO University, Kronverksky Pr. 49, St. Petersburg, 197101, Russia*

<sup>4</sup> *Centre de Recherche sur les Ions, les Matériaux et la Photonique (CIMAP), UMR 6252 CEA-CNRS-ENSICAEN, Université de Caen Normandie, 6 Boulevard Maréchal Juin, 14050 Caen Cedex 4, France*

<sup>5</sup> *Universitat Rovira i Virgili (URV), Física i Cristal·lografia de Materials i Nanomaterials (FiCMA-FiCNA), Marcel·lí Domingo 1, 43007 Tarragona, Spain*

<sup>6</sup> *Serra Hünter Fellow*

<sup>7</sup> *D.V. Efremov Institute of Electrophysical Apparatus, 196641 St. Petersburg, Russia*

## Abstract

The structure of multiphase transparent glass-ceramics prepared from glasses by controlled crystallization and of optical ceramics prepared by uniaxial recrystallization hot pressing are compared. Glass-ceramics and ceramics were doped with rare-earth (RE) and transition metal (TM) ions.

In the course of the glass-ceramics development, regions of structural inhomogeneity enriched in ZnO are formed in the initial glass. Their composition depends on the type and concentration of the TM and RE ion and determines the difference in phase assemblage of glass-ceramics. In optical ceramics, cobalt ion enter the structure of ZnO and form the CoO phase. RE ions do not enter the structure of ZnO crystals, but are located on their surface and form the RE<sub>2</sub>O<sub>3</sub> phase. ZnO optical ceramics doped with cobalt and RE ions should also be considered as multiphase materials.

**Keywords:** crystallization; ZnO; glass-ceramics; ceramics; rare-earth ions; transition metal ions

## Introduction

Zinc oxide powders, films, single crystals, ceramics and glass-ceramics, either undoped or doped with transition metal (TM) and rare-earth (RE) ions, are among the most actively studied materials [1-5]. This is due to the unique combination of their physical and chemical properties, such as a wide bandgap (3.37 eV), large exciton binding energy of 60 meV, high chemical, thermal

and mechanical stability, low toxicity, biocompatibility and biodegradability. Moreover, the properties of ZnO materials are tunable.

Zinc oxide is an efficient phosphor [6]. Various zinc oxide materials, as a rule, demonstrate two luminescence bands, i.e., a narrow band, which is located near the absorption edge of the ZnO crystal, so-called the near-band (NBE) emission, and a broad longer wavelength band, the maximum of which is usually in the green spectral range [6] but can be shifted to yellow and even red range. The latter band is called the deep band emission (DBE), or green luminescence (GL). The NBE luminescence with the decay time of about ns has an excitonic nature [7], while the GL with a much longer decay time has a defect nature [6]. UV light-emitters, scintillators, varistors, phosphors, piezoelectric transducers, gas-sensors, etc., have been developed on the base of these materials [3,5,6, 8,9]. ZnO is also used in pharmaceutical, cosmetics, textile and rubber branches of industry [9-11].

ZnO normally crystallizes in the hexagonal (wurtzite) crystal structure with lattice parameters  $a=3.25 \text{ \AA}$  and  $c= 5.21 \text{ \AA}$ . The  $\text{Zn}^{2+}$  ions are tetrahedrally coordinated by four  $\text{O}^{2-}$  ions. The hexagonal prism, positive and negative pedions and the hexagonal pyramid are simple forms characteristic of ZnO crystals [12,13]. The polar planes of pedions have an increased reactivity, which plays an important role in interaction of crystals with doping ions. It was demonstrated that the optical and luminescence characteristics of ZnO largely depend on the choice of the corresponding doping ions and the synthesis conditions and subsequent secondary treatments of the samples [6].

Growth of large ZnO single crystals of high optical quality is time-consuming and a laborious process [6]. The use of ZnO powder with typical particle agglomeration is complicated for many optical applications. The reproducibility of their properties is challenging. The usage of ZnO-based films is limited by optical losses in the substrate material, at the substrate-film interface and within the film. Therefore, the development of nanophase transparent glass-ceramics and optical ceramics based on ZnO crystals doped with transition metal (TM) and rare-earth (RE) ions for optoelectronics is important.

Preparation of transparent glass-ceramics by the melt-quenching technique with subsequent controlled crystallization and preparation of ceramics by the recrystallization mechanism during hot pressing, respectively, is not only much cheaper and technologically advanced than the growth of single crystals, but it also provides high uniformity of properties for relatively large-sized products. However, there is a difficulty in preparing transparent highly dense polycrystalline ZnO ceramics with anisotropic crystals of hexagonal symmetry. Anisotropic grains in the ceramics cause considerable light scattering at randomly oriented grain boundaries resulting in light losses in the bulk [6]. That is why such researches are limited [6,14-18].

Numerous attempts were made to create ZnO nanostructures (quantum dots, nanocrystals) in glasses of different systems. In [19], the authors observed a broad emission band around 396 nm in initial and heat-treated X-ray amorphous glass of the SiO<sub>2</sub>–B<sub>2</sub>O<sub>3</sub>–ZnO ternary system where the concentration of ZnO reached 60 mol%. The authors suggested this emission belongs to a ZnO nanophase not detected by XRD method, most probably to a trap-related emission situated at the aggregate–host interface and tried to prove it providing the XRD pattern of a sample crystallized after heating under the extreme conditions. The authors concluded that all the peaks of this material belong to ZnO crystals in different orientations (Fig. 1b of the ref. [19]). Meanwhile, the presented XRD pattern demonstrated peaks not of ZnO but of β- and α-willemite. Thus, the ZnO aggregation in the glass was not proven. In [20,21], the authors registered the UV emission in ZnO containing glasses of barium silicate [20,21], barium borate and barium germanate [20] systems and assumed it originated from ZnO aggregation. No experimental evidence of ZnO aggregation was provided. In [22], formation of “free ZnO” [22] was suggested in glasses of the SiO<sub>2</sub>–ZnO–BaO and the SiO<sub>2</sub>–ZnO–BaO–BaF<sub>2</sub> systems based on their photoluminescence spectra. The authors tried to confirm formation of “free ZnO” by the XRD pattern of the crystallized sample. The authors suggested the XRD pattern of the crystallized sample 7 (Fig. 4 of ref. [22]) presents ZnO while there is a mixture of β- and α-willemite. So, structural evidence of “free ZnO” formation was not provided. In [23], amorphous nanoscale ZnO clusters in oxynitride zinc phosphate glass were detected using TEM.

Surface crystallization of ZnO was demonstrated in [24–28] for materials based on the borate glass of the CaO–B<sub>2</sub>O<sub>3</sub>–ZnO–Al<sub>2</sub>O<sub>3</sub>–K<sub>2</sub>O–SiO<sub>2</sub> system. Surface crystallization of ZnO was also obtained in [29,30] in similar glasses. In [31], surface crystallization of willemite and zinc oxide was achieved. In [32], surface crystallization of ZnO in zinc-boro-oxy-fluoride was demonstrated. Thus, we came to conclusion that in all mentioned above systems volume crystallization of zinc oxide was not achieved.

There are several studies devoted to ZnO nanoparticles with size of about 3–6 nm obtained in SiO<sub>2</sub> matrix via a sol-gel route [33–36].

Partially crystallized samples with ZnO crystals were obtained in supercooled melts consisting of 70–80 mol% ZnO, up to 20 mol% B<sub>2</sub>O<sub>3</sub> and SiO<sub>2</sub> by Dimitriev et al. [37].

ZnO nanocrystals formed on the surface of glass of the ZnO–B<sub>2</sub>O<sub>3</sub>–SiO<sub>2</sub>–Sm<sub>2</sub>O<sub>3</sub> system by laser patterning were reported in [38]. In [39], the CO<sub>2</sub> laser-treated glasses of the CaO–B<sub>2</sub>O<sub>3</sub>–ZnO–Al<sub>2</sub>O<sub>3</sub>–K<sub>2</sub>O system demonstrated surface crystallization of Ag and ZnO nanocrystals.

Transparent glass-ceramics based on volume crystallized zincite (ZnO) nanocrystals were first obtained by L. Pinckney [40] in the  $K_2O$ -ZnO- $Al_2O_3$ - $SiO_2$  system. The compositions were designed as the ZnO component in a stoichiometric to subsiliceous leucite ( $K_2O \cdot Al_2O_3 \cdot 4SiO_2$ ) residual glass. L. Pinckney revealed that gallium can be substituted in part for aluminium and sodium in part for potassium without deteriorating properties and that contents of  $SiO_2$  higher than 50 wt% or  $Na_2O$  higher than 12 wt% tend to promote the crystallization of willemite ( $Zn_2SiO_4$ ) rather than ZnO [40]. The technique used by Pinckney is phase separation induced between alkali aluminosilicate and lower silica, high - zinc glasses. The low - silica phase extremely rich in ZnO, yields zincite from 5 to 20 nm in size upon heat-treatment to 750 °C [41]. In [40], the main features of the ZnO crystallization were revealed and doping of these glass-ceramics with TM and RE ions was discussed.

Up to now, in studies on volume crystallization of ZnO and spectroscopic properties of ZnO-containing transparent glass-ceramics, the authors [42-55] use the ideas and glass compositions suggested by L. Pinckney in ref. [40]. Space-selective precipitation of ZnO crystals by using high repetition rate femtosecond laser irradiation was reported in [56] for the glass with the composition of 45 $SiO_2$ -15 $Al_2O_3$ -25ZnO-15 $K_2O$  (mol%), which belongs to the system developed by L. Pinckney [40].

We have found only one excellent paper [57] wherein glass-ceramics containing ZnO nanosized crystals were obtained in a different system. Though it was formally the same potassium zinc aluminosilicate system, the difference with compositions presented in [40] was in the substitution of zinc oxide with zinc fluoride, which resulted in glass of the oxifluoride composition. It produced a significant difference in the phase composition of glass-ceramics: a mixture of ZnO and  $\beta$ - $Zn_2SiO_4$  precipitated simultaneously at the initial stage of heat-treatment, whereas sole crystallization of ZnO occurred when heat-treatments were performed at a higher temperature. This sequence of phase transformations is opposite to that presented in [40] and probably originates from the different mechanism of phase separation in the oxifluoride potassium zinc aluminosilicate system as compared with the oxide one.

Transparent glass-ceramics based on semiconducting ZnO crystals are self-nucleating materials due to liquid-liquid phase separation [40], which makes the sequence of phase transformations of initial glasses and properties of glass-ceramics extremely dependent on the preparation conditions (batch weight, crucible material, glass melting temperature, cooling rate, heat-treatment schedule) and purity of the raw materials. Optical properties of transparent glass-ceramics based on ZnO crystals are largely determined by the defect chemistry of the ZnO crystals that have relatively open structure and plenty of sites to accommodate intrinsic defects and extrinsic dopants. Optical properties of glass-ceramics are also determined by the preparation

conditions and purity of the raw materials. We would just like to state that in ref. [40] the batch weight was to yield about 1000 g of glass, glasses were melted in platinum crucibles at 1600 °C for 6 h, cast into patties about 1 cm thick, annealed at 575°C for 1 h and crystallized at temperatures of 700–800°C for 1–2 h. Later on, other researches used different preparation techniques to produce glass-ceramics of similar compositions. In [45] for a similar glass composition, quite a different preparation technique was used: the batch weight was 20 g, glasses were melted in alumina crucibles at 1500 °C for 2 h, subsequently quenched on a steel plate and crystallized at temperature of 750 °C for 3, 5, 10, 30, 60 and 120 min. In [53], the batch weight was 100 g, glasses were melted in alumina crucibles at 1580 °C for 2 h, subsequently quenched onto the preheated steel plate, annealed in a muffle furnace at 500 °C and crystallized at temperature of 730 °C for 0, 5, 8, 15, 30, 60 min. Thus, it is extremely important to analyze the preparation conditions while analyzing the properties of ZnO-based glass-ceramics prepared by different research groups.

The present work aims at comparing the structure of multiphase transparent glass-ceramics based on ZnO nanocrystals prepared from glasses of the K<sub>2</sub>O- ZnO-Al<sub>2</sub>O<sub>3</sub>-SiO<sub>2</sub> system by controlled crystallization and of ZnO optical ceramics produced by recrystallization high-temperature pressing and doped with RE and TM ions.

This paper is a tribute to Linda Pinckney.

## 2. Experimental

### 2.1. Preparation of glasses and glass-ceramics

We used initial glasses of two different compositions of the K<sub>2</sub>O – ZnO - Al<sub>2</sub>O<sub>3</sub> - SiO<sub>2</sub> system. The first composition (mol%) 12 K<sub>2</sub>O, 28 ZnO, 12 Al<sub>2</sub>O<sub>3</sub>, 48 SiO<sub>2</sub>, is similar to the composition Z4 listed in *Table 1, Compositions of transparent ZnO glass-ceramics*, of the ref. [40]. The second composition is (mol%) 14 K<sub>2</sub>O, 32 ZnO, 14 Al<sub>2</sub>O<sub>3</sub>, 40 SiO<sub>2</sub>. Batches of the first composition (Zn1) 200 g in weight were melted in a platinum crucible. Batches of the second composition (Zn2) 400 g in weight were melted in crucibles made of quartz ceramics.

The glass batches were prepared of reagent grade K<sub>2</sub>CO<sub>3</sub>, ZnO, Al<sub>2</sub>O<sub>3</sub> and SiO<sub>2</sub>. TM oxides (Co<sub>3</sub>O<sub>4</sub>, Cr<sub>2</sub>O<sub>3</sub>, Ni<sub>2</sub>O<sub>3</sub>, CuO), and RE oxides (Tm<sub>2</sub>O<sub>3</sub>, Er<sub>2</sub>O<sub>3</sub>, Yb<sub>2</sub>O<sub>3</sub>, Eu<sub>2</sub>O<sub>3</sub>, (Er<sub>2</sub>O<sub>3</sub>+Yb<sub>2</sub>O<sub>3</sub>), (Eu<sub>2</sub>O<sub>3</sub>+ Yb<sub>2</sub>O<sub>3</sub>) were added above 100 mol% of the base components. All the components were carefully mixed and placed into the crucible. Glasses were melted in a laboratory electric furnace at 1590 °C for 3 h with stirring, poured onto a cold metal plate and annealed at 500 or 550 °C. All glass-ceramics, undoped and doped with RE and TM oxides in concentration of 0.01-2.0 mol%, were prepared by secondary heat treatments of initial glasses in the temperature range from 680 to 1300 °C for 2 to 100 hours. The examples of transparent ZnO glass-ceramics, undoped and doped with TM and RE ions, are shown in Fig. 1.










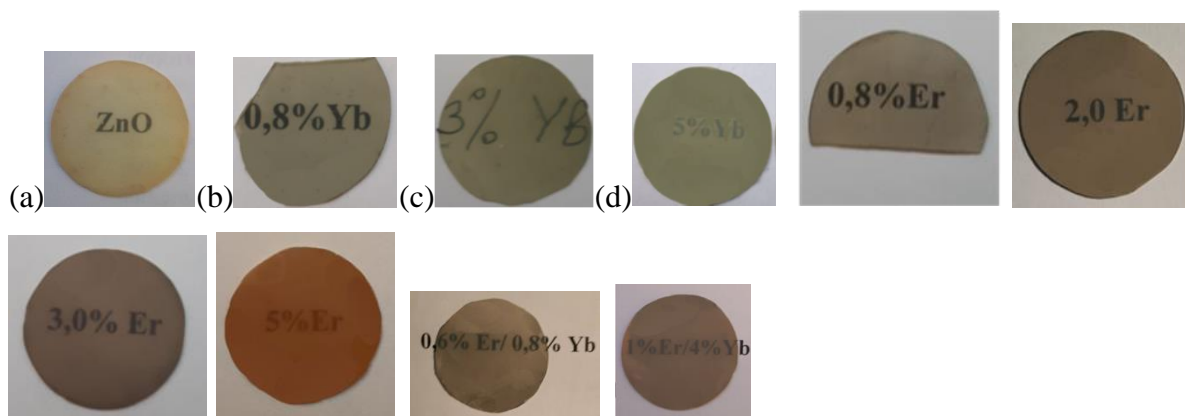
 No dopants	 0.1 mol% CoO	 0.1 mol% Cr <sub>2</sub> O <sub>3</sub> 700 °C/2h	NiO	 0.06 mol% CuO
 0.5 mol% Tm <sub>2</sub> O <sub>3</sub>	 0.1 mol% Er <sub>2</sub> O <sub>3</sub>	 0.1 mol% Yb <sub>2</sub> O <sub>3</sub> 750 °C/2h	Er+Yb	 0.5 mol% Eu <sub>2</sub> O <sub>3</sub>
 1 mol% Eu <sub>2</sub> O <sub>3</sub> +1.5 mol% Yb <sub>2</sub> O <sub>3</sub>				

Fig. 1. The images of transparent ZnO glass-ceramics, undoped and doped with TM and RE oxides. Numbers on the photographs denote heat-treatment schedule (°C/ h).

## 2.2. Preparation of ceramics

The undoped, Co-, Er-, Yb-doped and Er, Yb co-doped ZnO optical ceramics with the RE ions concentration of 0.1-5.0 wt% were fabricated from commercial reagent grade ZnO (purity: 3N, Zinsa, Peru), Co<sub>3</sub>O<sub>4</sub> and RE oxides of the same purity. The weighted portions of reagents were thoroughly mixed. The ceramics were prepared by uniaxial hot pressing (HPing) in vacuum at 1150 to 1220 °C. Both sides of the as-sintered ceramic disks were mirror polished using diamond slurry. After polishing, the disks had a diameter of 25 mm and a thickness of about 0.5 mm. The undoped ceramic is of yellow-green color. With Er<sup>3+</sup> and Yb<sup>3+</sup> doping, the color changed to rose and grey, respectively. The examples of transparent undoped, Er- and Yb-doped ZnO ceramics are shown in Fig. 2. The cobalt-doped ceramics are emerald-green colored. The color intensity increases with increasing the cobalt concentration in such a manner that the sample doped with 5% CoO is black.



**Figure 2.** Photographs of (a) undoped and (b-e) ZnO transparent ceramics with different Yb and Er doping levels (indicated by labels, in wt%).

### 2.3. Characterization methods

#### 2.3.1. Differential scanning calorimetry (DSC)

Glasses were characterized by differential scanning calorimetry (DSC) measurements performed on a simultaneous thermal analyzer NETZSCH STA 449 F3 Jupiter. The glass transition and crystallization temperatures were determined from about 15 mg bulk samples, using argon as a purging gas and a platinum crucible, with a heating rate of 10 °C/min, at the temperature range between room temperature and 1250 °C.

#### 2.3.2. X-ray diffraction (XRD)

XRD patterns of finely powdered initial glasses and glass-ceramics were measured using a Shimadzu XRD-6000 diffractometer with Cu K $\alpha$  radiation and a Ni filter (1.54056 Å). Taking into account that phase assemblage on the surface and in the volume of glass-ceramics can differ, XRD patterns, if necessary, were taken not only from the volume of the sample, but also from its surface. In this case, the volume and the surface of the sample were carefully separated. The XRD patterns were collected in a fixed time scan, sampling pitch: 0.02°, preset time: 6 s. We performed Rietveld refinement of the structure, phase compositions, volume fraction and sizes of nanocrystals using the Maud program [58]. Pure cubic Y<sub>2</sub>O<sub>3</sub> powder standard sample was used to correct the data for instrumental broadening. For modeling the residual glass [59], we used the leucite, KAlSi<sub>2</sub>O<sub>6</sub>. The mean crystal size and volume fraction of ZnO were determined. The error in the estimation of the mean crystal size is about  $\pm 2$  nm for  $D_{\text{XRD}}$  of about 20–30 nm [60]. The error in the estimation of the volume fraction of ZnO depends on the volume fraction and was estimated according to Ref. [59]. Parts of XRD patterns of the glass-ceramics after heat-treatments at 1200 and 1300 °C for 2



and 24 h were recorded in a scanning mode ( $2\theta=27.6-29.8^\circ$ ) with a sampling pitch of  $0.04^\circ$  and a 100 s preset time.

The XRD patterns of ceramic disks were measured using the same Shimadzu XRD-6000 diffractometer with a Ni-filtered Cu  $K_\alpha$  radiation. The samples were scanned according to a following mode: fixed time scan, scan speed 2.0 deg/min, sampling pitch:  $0.02^\circ$ , preset time: 3.0 s. To check whether crystals of rare-earth oxides were formed during sintering, additional XRD patterns were recorded in a special mode (fixed time scan, sampling pitch:  $0.01^\circ$ , preset time: 100 s) in an angular range of  $2\theta = 29.0-30.3^\circ$ , where the main diffraction peaks of cubic  $\text{Yb}_2\text{O}_3$  and  $\text{Er}_2\text{O}_3$  are located. With the aim to find the cobalt-containing crystalline phase, additional XRD patterns were also recorded in another special mode (fixed time scan, sampling pitch:  $0.03^\circ$ , preset time: 60 s) in the angular ranges of  $2\theta = 42.0-42.99^\circ$  and  $2\theta = 61.0-61.99^\circ$ , where the diffraction peaks of cubic CoO with Miller's indices ( $hkl$ ) (200) and (220), respectively, are located. The Rietveld refinement was performed using the Maud software [57].

For evaluating the preferred orientation of ZnO samples, the texture coefficient  $T_c(hkl)$  was used. It was calculated by the equation (1):

$$T_c(hkl) = \frac{I(hkl)/I_0(hkl)}{\left(\frac{1}{N}\right) \left[ \sum_N I(hkl)/I_0(hkl) \right]}, \quad (1)$$

where ( $hkl$ ) is the crystalline plane,  $I$  is the measured XRD intensity,  $I_0$  is the standard intensity of randomly oriented crystals according to a reference XRD card and  $N$  is the number of diffraction peaks [61]. From Eq. (1) it follows that  $T_c$  is close to unity for randomly oriented crystals, and it is greater than 1 when a certain ( $hkl$ ) plane is preferentially oriented.

### 2.3.3. Small angle X-ray scattering

Plane-parallel polished samples with thickness of 0.2 mm were studied by small angle X-ray scattering (SAXS) method. The SAXS intensity  $I(\varphi)$  was measured with a home-made instrument in the range of scattering angles  $\varphi$  from 6 to 450 arc min which corresponds to scattering vector range ( $Q$ ) from  $8 \cdot 10^{-3} \text{ \AA}^{-1}$  to  $0.5 \text{ \AA}^{-1}$  where  $Q = (4\pi/\lambda)\sin(\varphi/2)$ ,  $\lambda$  is the X-ray wavelength and  $\varphi$  is a scattering angle. Cu $K\alpha$  radiation ( $\lambda = 1.54 \text{ \AA}$ ) was used with an "infinitely" high primary beam ("infinitely" high slit).

SAXS curves of phase-separated glasses and glass-ceramics often exhibit maximum. It appears due to the regularity in a distribution of scattering regions in the glass volume. The value of  $Q$  corresponding to the maximum on the  $I(Q)$  curve ( $Q_0$ ) and the distance between centers of

regularly distributed particle ( $L$ ) are related as

$$L \cong (3.3 \div 3.5) 10^3 Q_0^{-1} \quad (2)$$

where  $L$  (in Å) is a distance between centers of regularly distributed particle [62]. The position of the maximum  $Q_m$  on the  $Q$  dependence of  $QI(Q)$  corresponds to the inverse radius of the scattering regions. For the monodisperse system of spherical particles with radius  $R$ , in condition of validity of Guineir equation [63]

$$R = \sqrt{\frac{5}{2}} Q_m^{-1} \quad (3).$$

#### 2.3.4. Electron microscopy

The structure of the initial glass and glass-ceramics was studied by the transmission electron microscopy (TEM) with the JEOL TEM-1011 microscope (100 kV acceleration voltage, 0.4 nm point resolution). For this study, fine powdered materials were dispersed in ethanol, and a drop containing a small amount of material in suspension was deposited onto a carbon-coated copper grid.

The morphology of ceramics was characterized by scanning electron microscopy (SEM) using Carl Zeiss EVO, TESCAN LYRAS and Carl Zeiss MERLIN microscopes. For this study, the surface of ceramics was preliminary etched in a mixture of hydrochloric and hydrofluoric acids. The same MERLIN microscope equipped with an Inca Energy X-Max analyzer was employed for energy dispersive X-ray (EDX) based element mapping. ~~The grain size distribution was analyzed with the ImageJ software.~~

#### 2.3.5. Raman spectroscopy

The Raman spectra were measured with a Renishaw inVia confocal Raman microscope equipped with the multichannel detector cooled down to  $-70$  °C using a Leica x50 objective (N.A. = 0.75). The accumulation time was 10 s and the number of accumulations was 30. The spatial resolution was about  $2 \text{ cm}^{-1}$ . The Raman spectra of glasses and glass-ceramics were recorded using the excitation wavelength  $\lambda_{\text{exc}}$  of 488 nm ( $\text{Ar}^+$  laser line). An edge filter was used.

The Raman spectra of ceramics were measured using the excitation wavelength  $\lambda_{\text{exc}}$  of 514 nm ( $\text{Ar}^+$  laser line).

#### 2.3.6. Optical spectroscopy

The optical absorption spectra of glasses, glass-ceramics and ceramics were measured in the spectral range from 300 to 3300 nm with a Shimadzu UV 3600 spectrophotometer with a spectral resolution of 1 nm (0.2 nm for the range of absorption bands of RE ions).

It should be taken into account that glass-ceramics are inhomogeneous materials (crystals in glass matrix) and scatter light. Thus, the measurement of optical density of a glass-ceramic sample is accompanied by falling the scattered light into a detector of the spectrophotometer that leads to an error in optical density measurement. The error depends on scattering characteristics and the acceptance angle of the spectrophotometer. We studied the problem of measuring optical density of nanostructured glass-ceramics samples by the spectrophotometer Shimadzu UV 3600 [64] and concluded that the error is negligible if the internal optical density of the sample caused by scattering,  $D_s$ , satisfies the condition

$$D_s \lesssim 2. \quad (4)$$


We checked the fulfilment of this condition in all our measurements of optical density of glass-ceramic samples.

### 3. Results

#### 3.1. Glasses and glass-ceramics

##### 3.1.1. The ZnO-based glass-ceramics are self-nucleating due to liquid-liquid phase separation and require no added nucleating agents [40].

SAXS is a powerful tool to study early stages of formation of inhomogeneity regions in glasses inclined to phase separation [63]. The potentiality of SAXS in the study of glass-ceramic structure was described in detail (for example, see [65] and references therein) The structure of the initial glass Zn1 doped by 0.05% CoO and ZnO-based glass-ceramics prepared from this glass by heat-treatments at 680 °C for 24 h and at 720 °C for 2 h was studied by SAXS. Fig. 3(a) shows SAXS intensity  $I$  as a function of the magnitude of scattering vector  $Q$ .

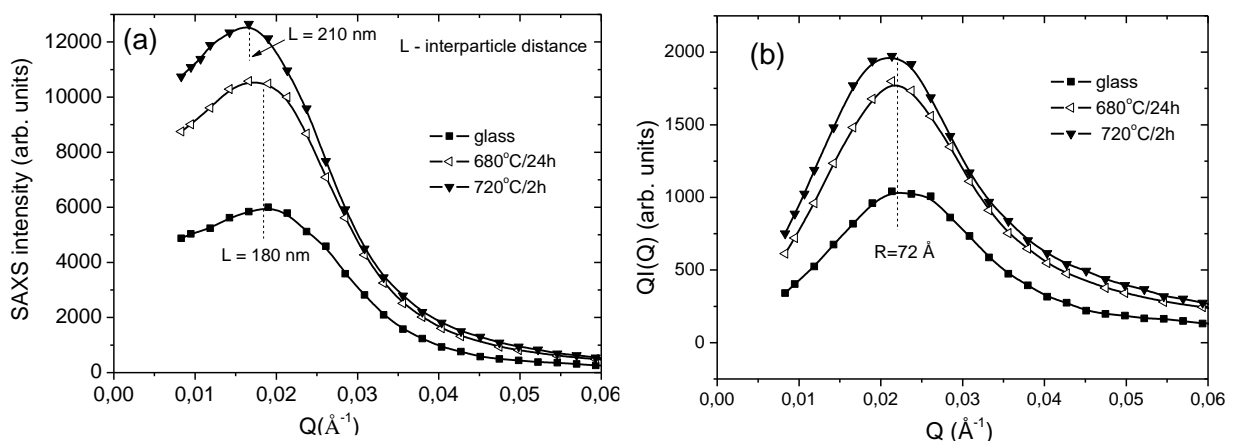

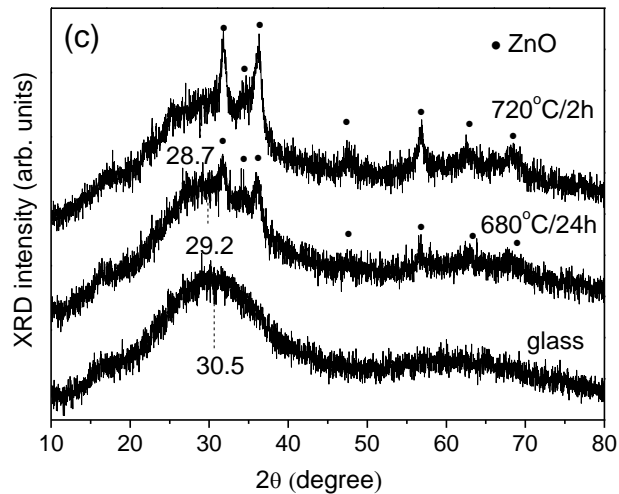


Fig. 3. SAXS curves and XRD patterns for the initial glass Zn1 doped with 0.05% CoO and glass-ceramics: (a) dependences of the SAXS intensity on  $Q$ ; (b) dependences of  $Q \cdot I(Q)$  on  $Q$ ; (c) corresponding XRD patterns. The dashed lines mark the positions of the maxima on the curves. The heat-treatment schedules are shown in figures.

According to SAXS (Fig. 3(a,b)) and XRD findings (Fig. 3(c)), the initial glass is inhomogeneous and X-ray amorphous. After heat-treatments, the SAXS intensity increases. The angular dependences of the SAXS intensity by the initial glass and the glasses heat-treated at 680 and 720 °C demonstrate pronounced maxima, see Fig. 3(a). After the heat-treatment of the initial glass at 680 °C for 24 h, the position of the maximum remains practically unchanged. According to Eq. (2), from the position of the maximum it follows that the mean interparticle distance is about 180 Å both in the initial glass and in glass-ceramics prepared by the heat-treatment at 680 °C for 24 h. The presence of a maximum on the angular dependence of the SAXS intensity by the initial glass can be considered as an evidence of spinodal phase decomposition that occurs during cooling of the glass melt [65]. The invariability of the position of this maximum after the heat-treatment at 680 °C for 24 h means that the space distribution of inhomogeneous regions formed in the glass during its casting and annealing is not changed during this heat-treatment. Heat-treatment at 720 °C for 2 h leads to a shift of the maximum on the SAXS curve to smaller angles, and the interparticle distance increases to 210 Å.

Fig. 3(b) shows the dependences of  $QI(Q)$  versus  $Q$  for the initial glass and glass-ceramics. The position of the maximum on the  $QI(Q)$  curve by the glass remains near constant after its heat-treatment at 680 °C for 24 h, i.e., the dimensions of the scattering regions formed in the initial glass remain unchanged and equal to  $\sim 70$  Å. Consequently, the increase in the SAXS intensity should be related to crystallization of ZnO within these inhomogeneous regions occurring during heat-treatment, see Fig. 3(c). When the glass was heat-treated at 680 °C for 24 h, the number of inhomogeneous regions did not change. The Ostwald ripening was not observed. Thus, the liquid

phase separation was actually completed during cooling of the melt. Crystallization occurs within the liquid phase-separated regions. The spinodal character of decomposition at melt quenching and annealing does not exclude the formation of a droplet structure at later stages of phase transformation during subsequent heat-treatments [66]. Crystallization occurs independently in each droplet.

*3.1.2. The compositions can be approximated as the ZnO component in a stoichiometric to subsiliceous leucite host glass... The microstructure of the transparent glass-ceramic comprises 5–20 nm crystals of ZnO dispersed uniformly throughout a continuous aluminosilicate glass [40].*

Fig. 4 shows Raman spectra of the initial and heat-treated glass Zn1 doped with 0.05% CoO. Note that their XRD patterns are listed in Fig. 3(c). Similar Raman spectra were presented by Du et al. in [56]. The Raman spectrum of the initial glass consists of the main band with peaks at 484, 572 and 714  $\text{cm}^{-1}$  and the high-frequency envelope with the maxima at  $\sim 872$ , and  $\sim 1000$   $\text{cm}^{-1}$ . According to [67], the band near 484  $\text{cm}^{-1}$  indicates Si-O-Al linkages, while the shoulder resolved at 572  $\text{cm}^{-1}$  implies the presence of Al-O-Al bridges [67,68], while the high-frequency envelope is due to the antisymmetric-stretching modes of O atoms and network-forming cations in the three-dimensional aluminosilicate framework [67,69]. After heat-treatment of the initial glass at 680 °C for 24 h, the new peaks appear at 96 and 438  $\text{cm}^{-1}$  that are assigned to the  $E_2^{\text{low}}$  and  $E_2^{\text{high}}$  modes of hexagonal ZnO crystals [70,71]. The shape of the high-frequency envelope in the spectrum of the sample is changed. Instead of the unresolved band at  $\sim 872$   $\text{cm}^{-1}$ , the peak at 867  $\text{cm}^{-1}$  appears. The higher frequency band broadens, see Fig. 4. After heat-treatment at 720 °C for 2 h, in addition to the peaks at 96 and 438  $\text{cm}^{-1}$  the tiny peak appears at 332  $\text{cm}^{-1}$ . This peak is assigned to  $E_2^{\text{low}}$  and  $E_2^{\text{high}}$  modes difference in Raman spectrum of ZnO crystals [70]. The appearance of small peaks at 166 and 310  $\text{cm}^{-1}$  as well as narrowing and intensification of the peak at 867  $\text{cm}^{-1}$  manifests the continuation of structure ordering within the silicate regions enriched in zinc. With further increasing the heat-treatment temperature, this ordering will result in additional crystallization of  $\beta$ -willemite,  $\beta$ - $\text{Zn}_2\text{SiO}_4$  [72]. The high frequency envelope in the Raman spectrum becomes broader due to appearance of the maximum at  $\sim 1054$   $\text{cm}^{-1}$ . This change can be explained by the increased connectivity of the aluminosilicate network caused by the ZnO crystallization [71,72]. We did not find the spectrum of glass with leucite composition in the literature, however, there is the spectrum of amorphous leucite obtained at high pressure [73] and its high-frequency envelope is consistent with those of the glass-ceramics obtained presented in Fig. 4. The Raman spectra of the  $\text{SiO}_2$ - $\text{KAlSi}_3\text{O}_8$  glass series [67] also demonstrate similar features.

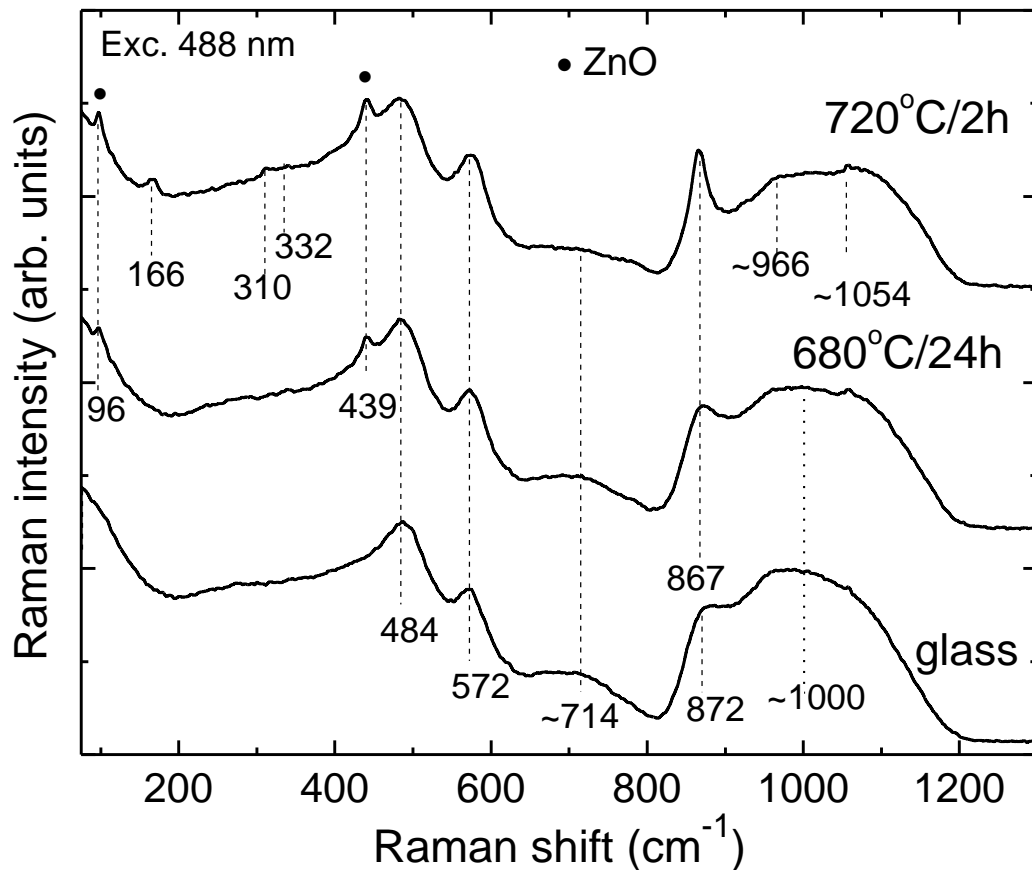


Fig. 4. Raman spectra (a) and XRD patterns (b) for the glass Zn1 doped with 0.05% CoO and glass-ceramics. The heat-treatment schedules are shown in figure.

An analysis of the position of the amorphous halo in the XRD patterns of the samples under study confirms these findings, see Fig. 3(c). The maximum of the diffuse X-ray scattering by the initial glass is at  $2\theta \approx 30.5^\circ$ . All components of the initial glass contribute to this scattering. During heat-treatments at 680 °C for 24 h and 720 °C for 2 h, ZnO crystals are formed in the glass. Crystallization of ZnO is accompanied by a change in the composition of the residual glass phase, as evidenced by the shift of the diffuse maximum to  $2\theta \approx 29.2^\circ$  and then to  $28.7^\circ$ . The main contribution to this scattering is made by potassium aluminosilicates. Note that the strongest diffraction peak in the XRD pattern of kalsilite is located at  $2\theta \approx 28.6$ ; other potassium feldspars also have strong lines in this angular range.

3.1.3. Zinc oxide is the first phase to crystallise as temperature increases, followed by the crystallisation and growth of willemite at the expense of ZnO and eventually to the surface crystallization of leucite ( $KAlSi_2O_6$ ) at the expense of the residual glass [40].

Fig. 5 shows a typical DSC curve by the example of the Z1 initial glass doped with 0.05% CoO. For this glass,  $T_g$  is at  $\sim 660$  °C, the ZnO onset crystallization temperature is  $\sim 760$  °C. The peak connected with crystallization of  $\beta$ -willemite ( $\beta$ - $Zn_2SiO_4$ ) appears at higher temperature of

about 800 °C but its onset crystallization temperature is difficult to determine because this peak superimposes on the peak of ZnO. The onset crystallization temperature of  $\alpha$ -willemite ( $\alpha$ - $\text{Zn}_2\text{SiO}_4$ ) is ~989 °C and that of leucite ( $\text{K}_2\text{O}\cdot\text{Al}_2\text{O}_3\cdot 4\text{SiO}_2$ ) is ~1120 °C.

This crystallization sequence is demonstrated in Fig. 5(a) by the example of the same Z1 glass doped with 0.05% CoO. No diffraction peaks are found in the XRD pattern of the initial glass indicating that it is X-ray amorphous. The first phase to crystallize is ZnO; it appears during heat-treatments at temperature of 680 - 720 °C. The mean ZnO crystal sizes determined using the Scherrer equation are about 10 - 11 nm. Heat-treatments in the temperature range of 750 – 900 °C resulted in crystallization of a mixture of ZnO and  $\beta$ - $\text{Zn}_2\text{SiO}_4$  nanocrystals. Their mean sizes determined with the Scherrer equation are about 10 - 12 nm and 11-14 nm, respectively, depending on the heat-treatment temperature [69].  $\alpha$ -willemite crystallizes at 950 °C at the expense of ZnO and  $\beta$ - $\text{Zn}_2\text{SiO}_4$ . During heat-treatment at 1000 °C, leucite ( $\text{K}_2\text{O}\cdot\text{Al}_2\text{O}_3\cdot 4\text{SiO}_2$ ) additionally crystallizes from the surface, while kalsilite ( $\text{K}_2\text{O}\cdot\text{Al}_2\text{O}_3\cdot 2\text{SiO}_2$ ) crystallizes in the volume of glass-ceramic, see Fig. 4(b). At elevated temperatures, the main crystalline phases are  $\alpha$ -willemite and leucite while the traces of kalsilite are still observed, see Fig. 4(a).

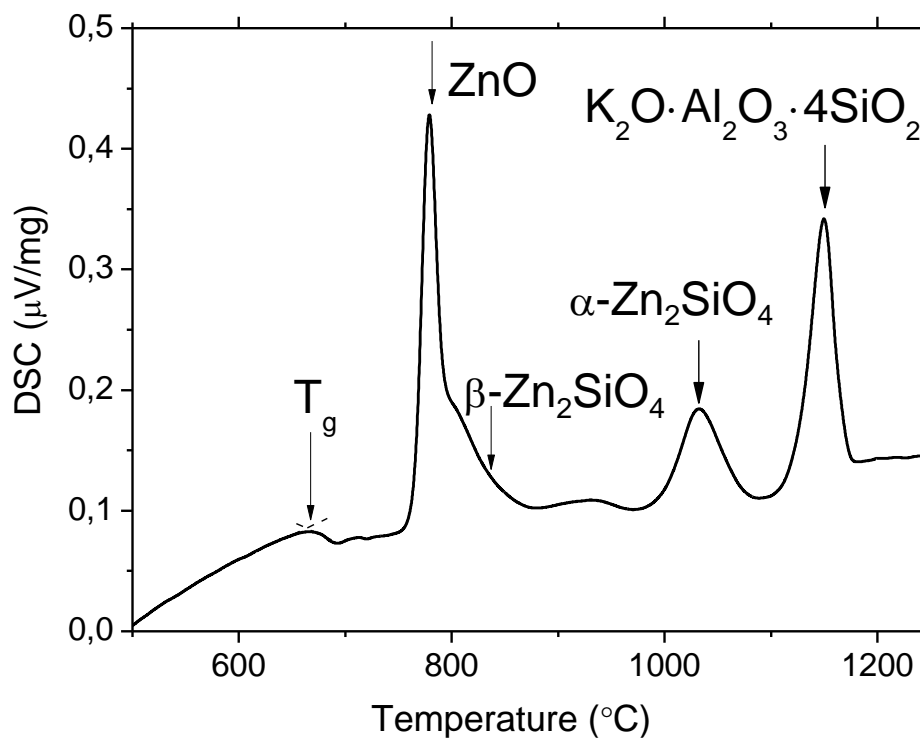


Fig. 5. DSC curve for the glass Zn1 doped with 0.05% CoO.

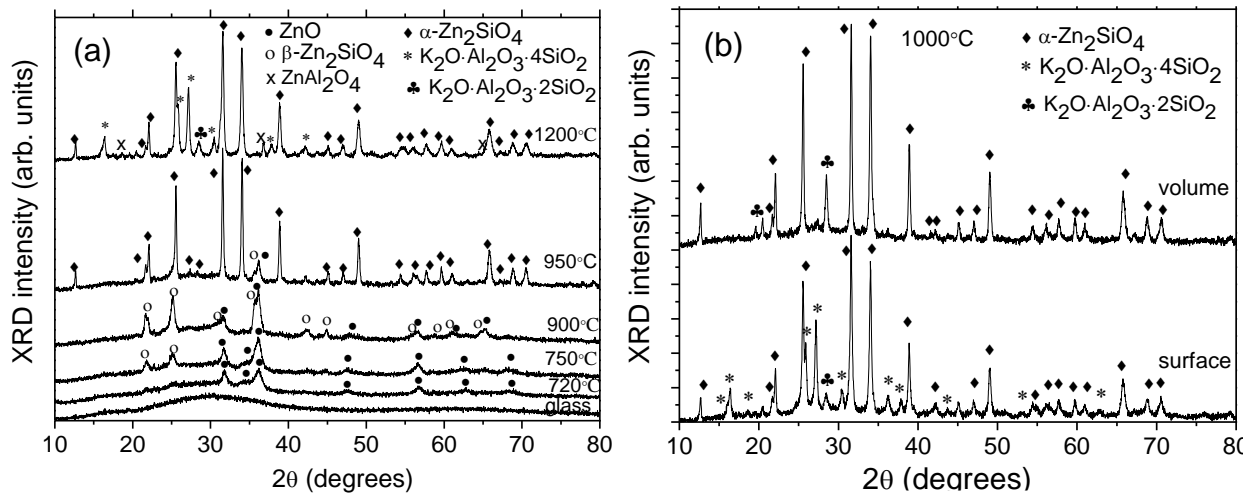


Fig. 6. XRD patterns of the glass Zn1 doped with 0.05% CoO. Heat-treatment temperatures are listed in the figure. Heat-treatment time is 2 h.

3.1.4. Transition metal ions do partition into the tetrahedral sites of ZnO in these glass-ceramics [40].

Cobalt-doped glass-ceramics

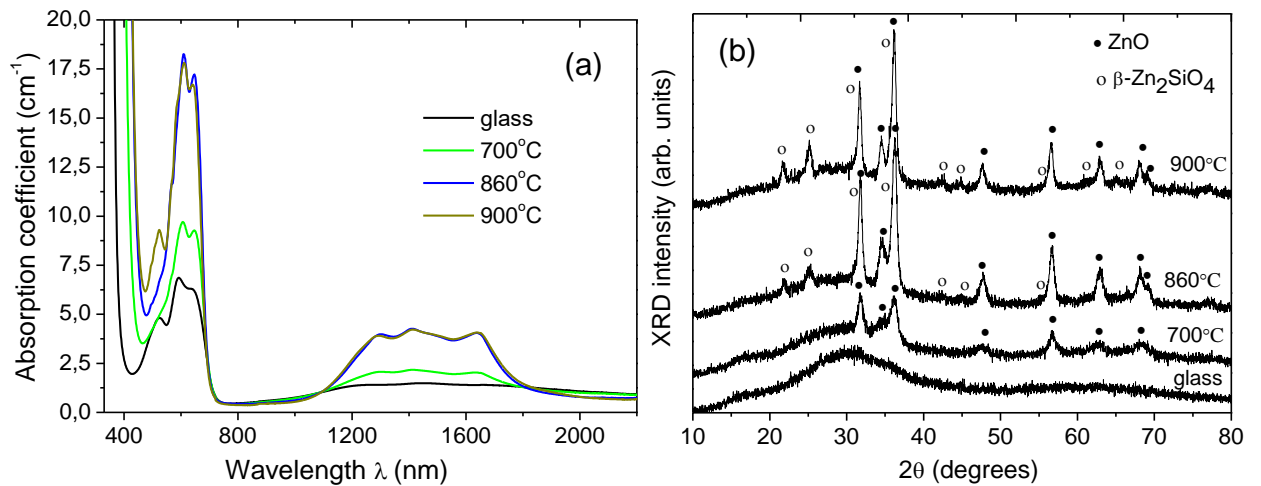



Fig. 7. Absorption spectra (a) and corresponding XRD patterns (b) of the initial and heat-treated glass Zn1 doped with 0.1% CoO. Heat-treatment temperatures are listed in the figure. Heat-treatment time is 2 h.

Fig. 7(a,b) presents absorption spectra and corresponding XRD patterns of the initial and heat-treated glass Zn1 doped with 0.1 mol% CoO. The spectrum of the initial glass, see Fig. 7(a), contains two broad absorption bands, one with maxima at 525, 590, and 640 nm, and the other in



the range of 1100–1700 nm. It is characteristic of  $\text{Co}^{2+}$  ions in a mixture of coordination sites: in octahedral, in distorted tetrahedral coordination, and possibly in five-fold coordinated sites. This type of spectrum is typical for  $\text{Co}^{2+}$  ions in aluminosilicate glasses [71]. A change in the absorption spectrum of the sample is observed after its heat-treatment at 700 °C for 2 h. There is a reduction of absorption at  $\sim 525$  nm and appearance of a shoulder at  $\sim 565$  nm and absorption bands at 607 and 643 nm while the broad band in the 1.2–1.7  $\mu\text{m}$  range becomes narrower and demonstrates peaks located at  $\sim 1.29$ , 1.42, 1.49, and 1.64  $\mu\text{m}$ . This change is caused by crystallization of ZnO and entering the tetrahedral sites in these nanocrystals by the  $\text{Co}^{2+}$  ions. The observed absorption bands match those for  $\text{Co}^{2+}:\text{ZnO}$  [74-76] and they are attributed to d-d transitions of  $\text{Co}^{2+}$  ions with  $3d^7$  high-spin configuration in a tetrahedral ligand field formed by neighboring oxygen ions in ZnO nanocrystals [71,72]. The absorption peaks in the visible range are assigned to  ${}^4\text{A}_2(\text{F}) \rightarrow {}^2\text{E}(\text{G})$ ,  ${}^4\text{A}_2(\text{F}) \rightarrow {}^4\text{T}_1(\text{P})$ , and  ${}^4\text{A}_2(\text{F}) \rightarrow {}^2\text{A}_1(\text{G})$  transitions. The absorption band in the infrared is associated with the electronic transitions from the  ${}^4\text{A}_2(\text{F})$  ground-state to the  ${}^4\text{T}_1(\text{F})$  excited multiplet. Intensities of these peaks constantly increase with heat-treatments at temperatures up to 860 °C and correspond to increasing the volume fraction of ZnO nanocrystals. Appearance of the peak at 523 nm in the spectrum of the glass-ceramic prepared by the heat-treatment at 900 °C is connected with  $\text{Co}^{2+}$  absorption both in octahedral and in distorted tetrahedral sites in  $\beta$ -willemite crystals [72].

#### Nickel-doped glass-ceramics

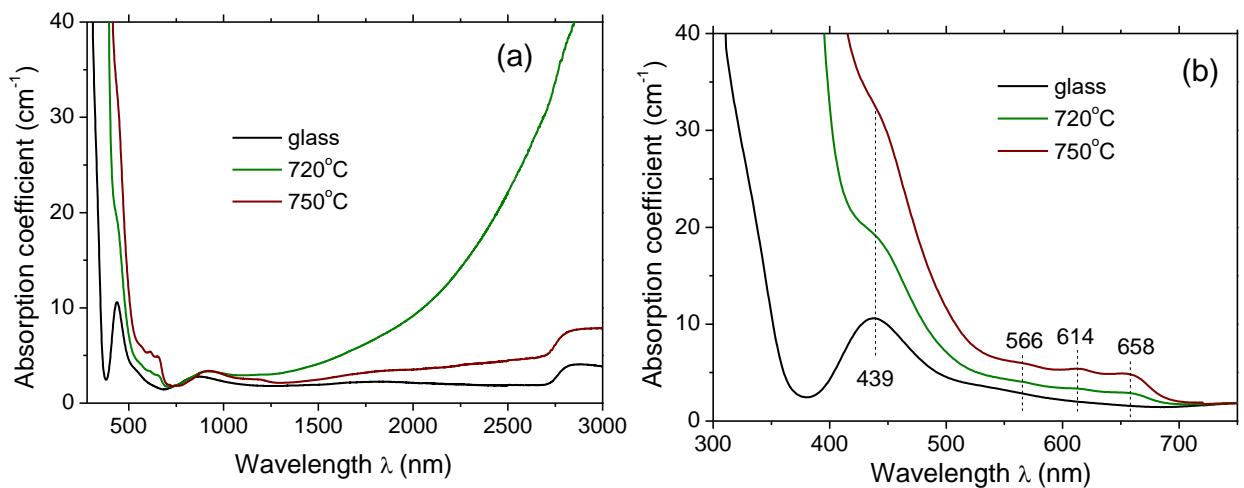

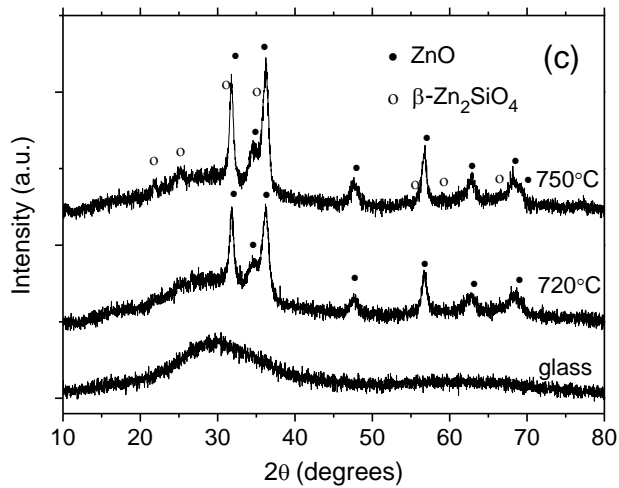


Fig. 8. Absorption spectra (a,b) and corresponding XRD patterns (c) of the initial and heat-treated glass Zn1 doped with 0.2 mol% NiO. Heat-treatment temperatures are listed in the figure. Heat-treatment time is 2 h.


*The absorption peaks coincide with those reported by Pappalardo et al for tetrahedrally coordinated Ni<sup>2+</sup> in ZnO, indicating that at least some of the Ni<sup>2+</sup> ions have partitioned into the ZnO crystals [40].*

Fig. 8(a-c) presents absorption spectra and corresponding XRD patterns of the initial and heat-treated glass Zn1 doped with 0.2 mol% NiO. The absorption spectrum of the initial glass presents three broad asymmetric absorption bands centered at about 439, 870 and 1830 nm, which is typical for Ni-doped aluminosilicate glasses and can be assigned to absorption of trigonal bipyramid fivefold Ni<sup>2+[VI]</sup> and tetrahedral fourfold species [77] with the predominance of Ni<sup>2+[VI]</sup> species. A change in the absorption spectrum of the sample is observed after its heat-treatment at 720 °C for 2 h. The absorption edge is shifted to longer wavelengths in such a manner that the absorption band with the maximum at 439 nm becomes partly concealed, new bands appear at 566, 614, 658, 742, ~920 nm, and ~1199, the raise of absorption at wavelengths longer than 1000 nm is revealed. Maximum of this IR absorption is not detected up to 3300 nm, which is the measurement limit of the spectrophotometer. These spectral changes are connected with crystallization of ZnO, see Fig. 8(c), and partition of Ni<sup>2+</sup> ions in these crystals [40]. Indeed, Pappalardo *et al.* [78] suggested that in ZnO, the Ni<sup>2+</sup> impurity ions are present in sites possessing tetrahedral symmetry with a slight axial deformation. The crystal field parameter  $Dq_{tet} \approx 380 \text{ cm}^{-1}$ . The absorption peaks of Ni<sup>2+</sup> ions in ZnO are located at 576, 616, 656, 742, and 1192 nm [79]. These peak positions are very similar to those in spectrum of the glass-ceramic sample, see Fig. 8(b). The raise of absorption in the IR is related to the presence of free carriers in semiconductor ZnO nanocrystals [80]. Thus, the spectrum is a superposition of spectra of Ni<sup>2+</sup> ions in ZnO crystals, in the residual glass and of the ZnO spectral features.

It confirms the statement that all glass-ceramics doped with TM ions *exhibit a significant colour change upon crystallisation consistent with a change in crystal field environment of the dopant ions, although part of the color change can be attributed to the crystallisation of ZnO itself* [40].

Absorption spectrum of glass-ceramic changes after heat-treatment of the glass at 750 °C. The absorption edge is shifted to even longer wavelengths, intensity of absorption bands with maxima at 566, 614 and 658 nm increases, intensity of the peak with maximum at ~920 nm remains near constant, and the peak appears at 1185 nm, see Fig. 8(a,b). IR absorption caused by the presence of free carriers in ZnO pronouncedly decreases. We assign these spectral changes to some increase in the ZnO crystallinity fraction and, to the larger extent, to crystallization of  $\beta$ -willemite, see Fig. 8(c). In literature, information about the reflectance spectrum of  $\text{Ni}^{2+}:\text{Zn}_2\text{SiO}_4$ ,  $\alpha$ -willemite, is evaluable [80]. The spectrum exhibits a wide, intense band in the range of 480-760 nm with absorption maxima at 540, 584, and 633 nm, which corresponds to  ${}^3\text{T}_1(\text{F}) \rightarrow {}^3\text{T}_1(\text{P})$  d-d transition in the tetrahedral environment. We cannot exclude the presence of these peaks in broad absorption bands of glass-ceramic prepared by heat-treatment at 750 °C. It should be taken into account that in  $\beta$ -willemite  $\text{Ni}^{2+}$  ions can enter both octahedral and in distorted tetrahedral sites crystals. We can find the attributes of  $[\text{VI}]\text{Ni}^{2+}$  in the spectrum of glass-ceramics. According to Pappalardo, the crystal field parameter  $Dq_{\text{oct}} \approx 860 \text{ cm}^{-1}$  [78]. Previously, we built the Tanabe-Sugano diagram for  $[\text{VI}]\text{Ni}^{2+}$  ion in the assumption that  $Dq = 860 \text{ cm}^{-1}$  and  $B = 890 \text{ cm}^{-1}$  [81]. The following maximum positions were presented: less than  $400 \text{ cm}^{-1}$ , 690, 790, and 1160 nm. Thus, the spectrum can be assigned to  $[\text{IV}]\text{Ni}^{2+}$  species in ZnO and  $\beta$ -willemite crystals, to  $[\text{VI}]\text{Ni}^{2+}$  in  $\beta$ -willemite crystals, and to  $[\text{VI}]\text{Ni}^{2+}$  species in the residual glass. A decrease of the IR absorption could be related to a beginning of  $\beta$ -willemite crystallization at the expense of ZnO.

#### Chromium-doped glass-ceramics

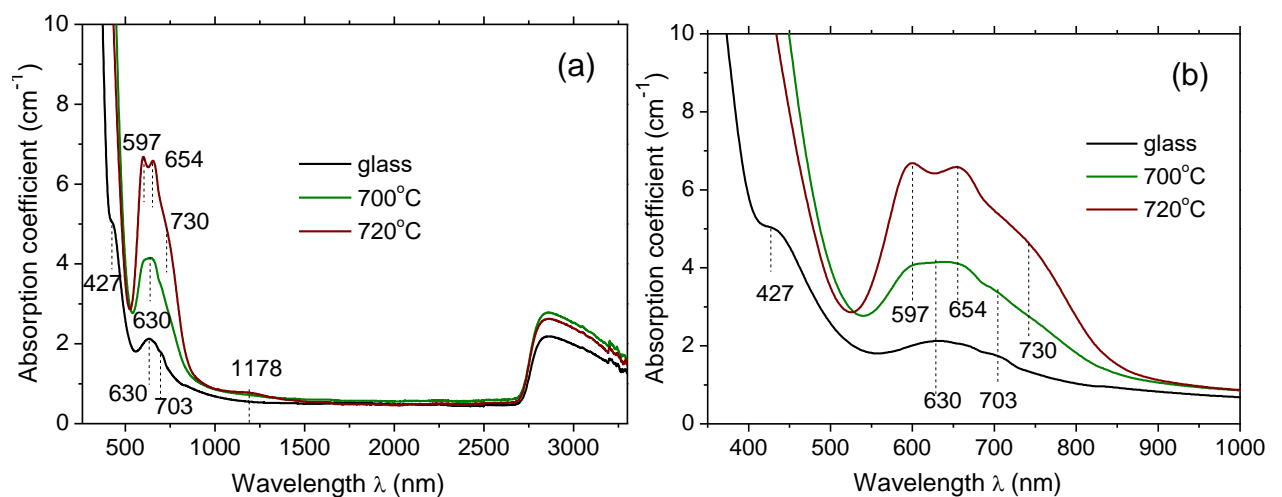

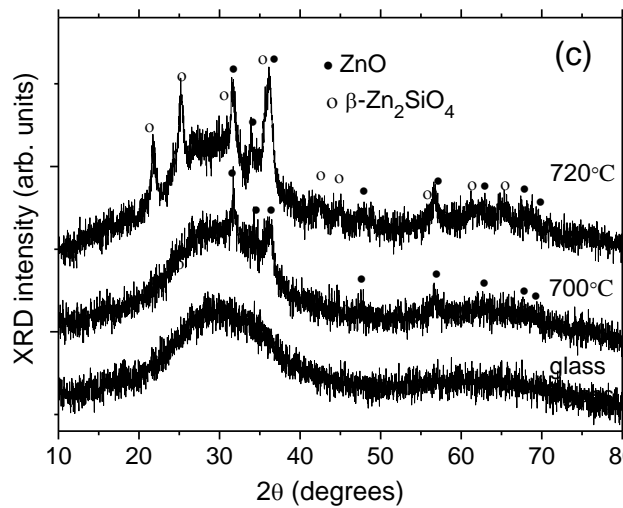


Fig. 9. Absorption spectra (a,b) and corresponding XRD patterns (c) of the initial and heat-treated glass Zn1 doped with 0.1 mol% Cr<sub>2</sub>O<sub>3</sub>. Heat-treatment temperatures are listed in the figure. Heat-treatment time is 2 h.

The absorption spectrum of the Zn1 glass doped with 0.1 mol% Cr<sub>2</sub>O<sub>3</sub> contains two broad absorption bands with maxima at 427 and 630 nm, see Fig. 9(a,b). This spectrum is typical for Cr<sup>3+</sup> ions in d<sup>3</sup> configuration in octahedral sites in silicate and aluminosilicate glasses and corresponds to the interconfigurational transitions from the <sup>4</sup>A<sub>2</sub> ground state to the <sup>4</sup>T<sub>1</sub> and <sup>4</sup>T<sub>2</sub> excited states, respectively [82]. There is also the inflection at 703 nm which corresponds to spin and parity forbidden transitions <sup>4</sup>A<sub>2</sub>→(<sup>4</sup>T<sub>1</sub>, <sup>2</sup>E). The ligand field strength Dq is ~1590 cm<sup>-1</sup>, the Racah parameter B is ~827 cm<sup>-1</sup> [83]. In the IR spectral range there is only a broad asymmetric band due to absorption of OH-groups dissolved in the melt during glass melting. Appearance of a small amount of ZnO nanocrystals, see Fig. 9(c), leads to a pronounced change in the absorption spectrum of the sample. Absorption edge is shifted to longer wavelengths, the band with a maximum at ~630 nm increases in intensity. A close look at this band allows to reveal two additional maxima at 597 and 654 nm, see Fig. 9(b). In the assignment of this absorption spectrum we referred to a paper of B. Babu *et al.* [84], wherein the optical absorption spectrum of Cr<sup>3+</sup> doped ZnO nanopowder is presented. The authors confirm the Cr<sup>3+</sup> in ZnO crystals are in octahedral site symmetry in host ZnO lattice. Two bands observed at 426 nm and 588 nm were assigned to the transitions <sup>4</sup>A<sub>2g</sub>(F) → <sup>4</sup>T<sub>1g</sub>(F) and <sup>4</sup>A<sub>2g</sub>(F) → <sup>4</sup>T<sub>2g</sub>(F), respectively. The weak absorption band observed at 702 nm was attributed to spin forbidden transition <sup>4</sup>A<sub>2g</sub>(F) → <sup>2</sup>E<sub>g</sub>(G). The ligand field parameters were determined as Dq = 1700 cm<sup>-1</sup>, and B = 636 cm<sup>-1</sup>. Based on these findings, we assigned the peaks in the spectrum of glass-ceramic prepared at 700 °C for 2 h to absorption of Cr<sup>3+</sup> ions distributed between the octahedral sites in the ZnO crystals and in the residual glass, see Fig. 9(c).

Glass-ceramic sample prepared by the heat-treatment at 720 °C for 2 h is a three phase system as it contains the crystals of ZnO and  $\beta$ -willemite distributed within the residual glass. The absorption spectrum of the glass-ceramics changes pronouncedly, the intensity of the absorption band rapidly increases while its shape changes. band see Fig. 9(b). There are two peaks with maxima at 597 and 654 nm, the inflection at  $\sim$ 730 nm and a weak peak at 1178 nm, see Fig. 9(a,b). This spectrum is also assigned to  $\text{Cr}^{3+}$  ions in octahedral site symmetry and shows the two bands centered at 420 nm (concealed behind the absorption edge) and 590 nm that arise from the spin allowed electronic transitions from  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_1$  and  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_2$ , respectively and the spin forbidden transitions from  ${}^4\text{A}_2 \rightarrow {}^2\text{T}_1(\text{t}_3)$  and  ${}^4\text{A}_2 \rightarrow {}^2\text{E}$  at 654 nm and 730 nm, respectively [85]. B Babu *et al.* calculated the ligand field parameters  $Dq = 1725.3 \text{ cm}^{-1}$ , and the Racah parameter  $B = 696.2 \text{ cm}^{-1}$ . It should be mentioned that the spectra of  $\text{Cr}^{3+}$  in ZnO- and  $\beta$ -willemite-based glass-ceramics closely resemble those in  $\text{Cr}^{3+}$ -doped  $\text{MgAl}_2\text{O}_4$  [86] and  $\text{Cr}^{3+}$ -doped  $\text{ZnAl}_2\text{O}_4$  [87], wherein  $\text{Cr}^{3+}$  ions are six-fold coordinated. In ref. [85] it was stated that  $\text{Cr}^{3+}$  has a very low solubility in  $\text{Zn}_2\text{SiO}_4$  and that additional spinel phases are easily formed. So we demonstrated difficulty in incorporation of octahedrally coordinated TM ions into the structure of ZnO crystals. In future, the detailed XRD analysis should be conducted to reveal the secondary spinel phases, if any.

*Large rare earth ions are unlikely to enter the ZnO crystals and would remain in the residual glass phase after crystallization [40].*

Initial Zn<sub>2</sub> glasses co-doped with  $\text{Er}_2\text{O}_3$  and  $\text{Yb}_2\text{O}_3$  are rose colored, coloration intensifies with increasing the Er doping concentration. The center of the glass co-doped with 0.2%  $\text{Er}_2\text{O}_3$  and 0.2%  $\text{Yb}_2\text{O}_3$  has a slightly yellow coloration, see Fig. 10.

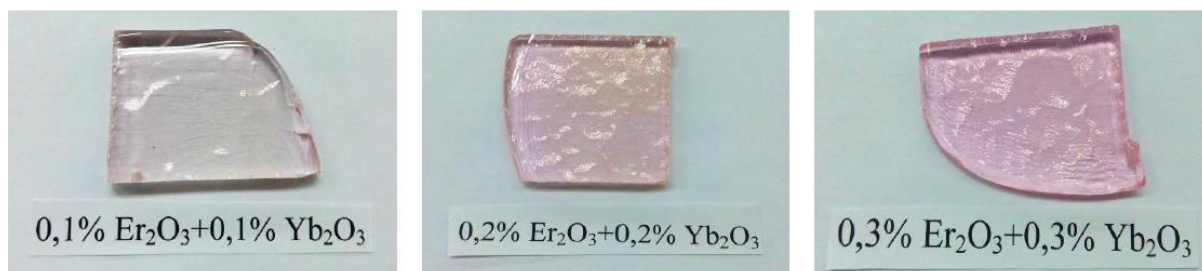


Fig. 10. 8. Images of the initial Zn<sub>2</sub> glasses doped with (a) 0.1%  $\text{Er}_2\text{O}_3$  and 0.1%  $\text{Yb}_2\text{O}_3$ ; (b) 0.2%  $\text{Er}_2\text{O}_3$  and 0.2%  $\text{Yb}_2\text{O}_3$ ; (c) 0.3%  $\text{Er}_2\text{O}_3$  and 0.3%  $\text{Yb}_2\text{O}_3$ .

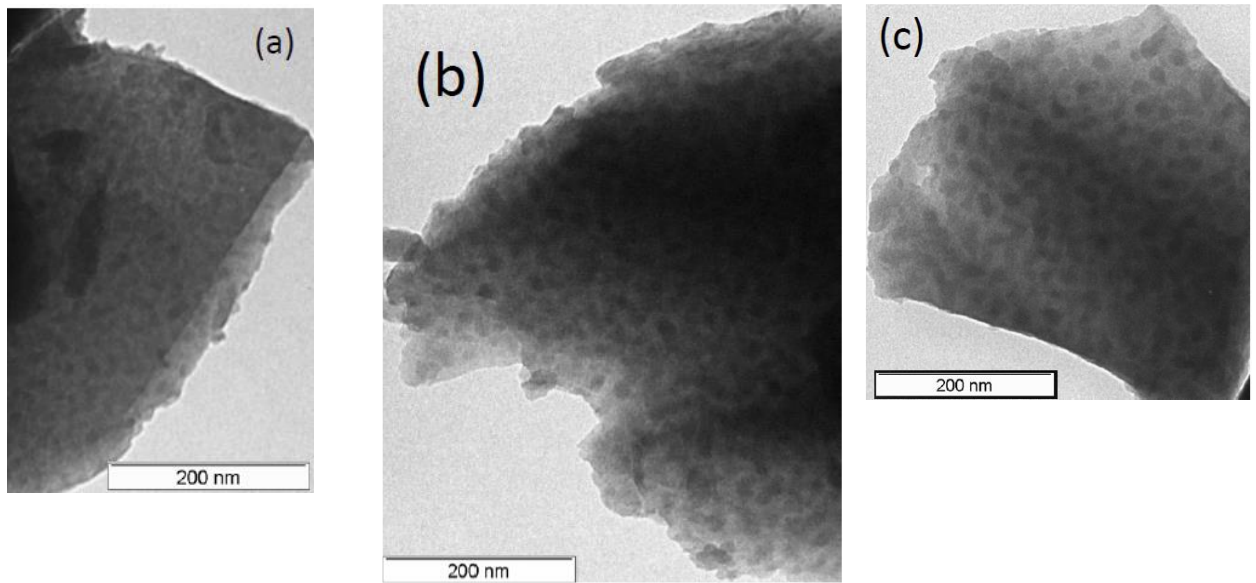


Fig. 119. TEM images of the initial Zn glasses doped with (a) 0.1%  $\text{Er}_2\text{O}_3$  and 0.1%  $\text{Yb}_2\text{O}_3$ ; (b) 0.2%  $\text{Er}_2\text{O}_3$  and 0.2%  $\text{Yb}_2\text{O}_3$ ; (c) 0.3%  $\text{Er}_2\text{O}_3$  and 0.3%  $\text{Yb}_2\text{O}_3$ .

The TEM images (Fig. 11) of these glasses reveal a near-uniform distribution of dark regions of inhomogeneity, which confirms the phase separation for all examined initial glasses. From the comparison of their XRD patterns and absorptions spectra it follows that the doping level of  $\text{RE}^{3+}$

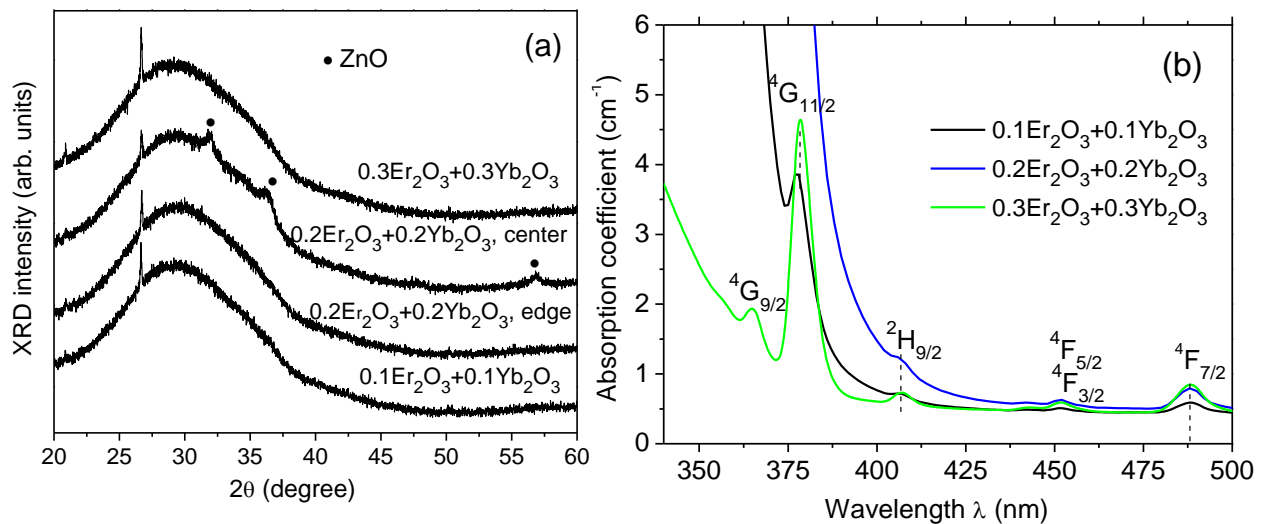


Fig. 1210. XRD patterns (a) and absorption spectra (b) of the initial Zn glasses co-doped with  $\text{Er}_2\text{O}_3$  and  $\text{Yb}_2\text{O}_3$ . The  $\text{Er}_2\text{O}_3$  and  $\text{Yb}_2\text{O}_3$  doping level is indicated in figure.

ions drastically influences the glass structure. An addition of 0.2/0.2 mol%  $\text{Er}_2\text{O}_3/\text{Yb}_2\text{O}_3$  provokes crystallization of ZnO, which causes the location of the absorption edge at about 380 nm. The glasses co-doped with 0.1/0.1 and 0.3/0.3 mol%  $\text{Er}_2\text{O}_3/\text{Yb}_2\text{O}_3$  are amorphous and liquid phase separated, see Fig. 12(a). However, a striking difference in the position of absorption edges in their absorption spectra reflects different compositions of these regions. We speculate that in the glass

doped with 0.1/0.1 mol% Er<sub>2</sub>O<sub>3</sub>/Yb<sub>2</sub>O<sub>3</sub> amorphous regions of inhomogeneity are enriched in ZnO while the introduction of 0.3/0.3 mol% Er<sub>2</sub>O<sub>3</sub>/Yb<sub>2</sub>O<sub>3</sub> leads to segregation of RE<sup>3+</sup> ions into the phase-separated regions that results in deluting the Zn content and retarding the ZnO crystallization. Doping of the glass with different concentrations of Er<sub>2</sub>O<sub>3</sub> and Yb<sub>2</sub>O<sub>3</sub> modifies the kinetics of crystallization of ZnO. Transparent glass-ceramics obtained by the heat-treatment at 720 °C contain ZnO nanocrystals, the sample doped with 0.2/0.2 mol% Er<sub>2</sub>O<sub>3</sub>/Yb<sub>2</sub>O<sub>3</sub> has the highest fraction of ZnO.

To estimate the effect of crystallization on spectral properties of ZnO-based glass-ceramics doped with RE<sub>2</sub>O<sub>3</sub>, we analyzed the difference between optical densities of samples of the heat-treated and initial glass with approximately the same thickness  $h$  for a number of heat treatments. The analysis of the difference allowed us to exclude the reflection losses because the change in reflection caused by crystallization was estimated to be negligible. The difference between the optical density  $D_{GC}$  of the heat-treated (glass-ceramic, GC) sample and the optical density  $D_{IG}$  of the initial glass sample was used for the estimation of the extinction coefficient

$$\alpha_{ZnO} = (D_{GC} - D_{IG}) / (h \log_{10} e) \cong 2.3026 (D_{GC} - D_{IG}) / h \quad (5)$$

related to scattering and absorption originated from ZnO nanocrystals.

Three effects of ZnO crystallization on extinction coefficient  $\alpha_{ZnO}$  of glass-ceramics doped with RE ions were demonstrated. First, ZnO nanocrystals cause a significant scattering of visible light. Second, the absorption band at long wavelengths ( $\lambda > 1000$  nm) was observed which is related to the presence of free carriers in semiconductor ZnO nanocrystals [80] and is generally discussed in terms of localized surface plasmon resonance (LSPR). Finally, a fine effect of the changes in intensities and positions of Er<sup>3+</sup> and Yb<sup>3+</sup> absorption peaks was demonstrated for the first time using the analysis of difference of optical densities (Eq. (5)). Namely, we found that the changes in intensities and positions of Er<sup>3+</sup> and Yb<sup>3+</sup> absorption peaks in the course of the ZnO crystallization are observed for a number of concentrations of Er<sub>2</sub>O<sub>3</sub> and Yb<sub>2</sub>O<sub>3</sub> additions in the interval 0.05–2 mol% (including mixed compositions  $x(\text{Er}_2\text{O}_3 + \text{Yb}_2\text{O}_3)$ ,  $x=0.2-1$  mol%). This means that that the surrounding of RE ions slightly differ in the initial glass and the glass-ceramics based on ZnO nanocrystals.

For illustration, the full absorption spectra and the extinction coefficients  $\alpha_{ZnO}$  in vicinity of two absorption peaks of glass-ceramics containing (0.3 mol% Er<sub>2</sub>O<sub>3</sub> + 0.3 mol% Yb<sub>2</sub>O<sub>3</sub>) are presented in Fig. 13(a-c). The corresponding XRD patterns are demonstrated in Fig. 11(d). The unit cell parameters  $a$  and  $c$  and average sizes of ZnO crystals in glass-ceramics obtained by different heat-treatments are listed in Table 1.

Table 1. The unit cell parameters and average sizes of ZnO crystals in glass-ceramics containing

(0.3 mol% Er<sub>2</sub>O<sub>3</sub> + 0.3 mol% Yb<sub>2</sub>O<sub>3</sub>) and obtained by different heat-treatments.

Heat-treatment schedule, °C / h	The ZnO unit cell parameters (Å)		The average size of ZnO crystals (nm)
	<i>a</i> (±0.003)	<i>c</i> (±0.003)	
680/12	traces	traces	10.0
680/48	3.255	5.229	13.5
700/2	3.256	5.227	17.0
720/2	3.256	5.227	17.0

Fig. 13(b) shows that crystallization does not significantly change the position of Er<sup>3+</sup> absorption peak at  $\lambda \cong 520$  nm whereas it appreciably reduces the intensity of this peak for all heat treatments. The intensity of the absorption peak of Yb<sup>3+</sup> ( $\lambda \cong 978$  nm) does not change significantly due to crystallization while this peak is shifted to short wavelengths (Fig. 11(c)) for all heat treatments.

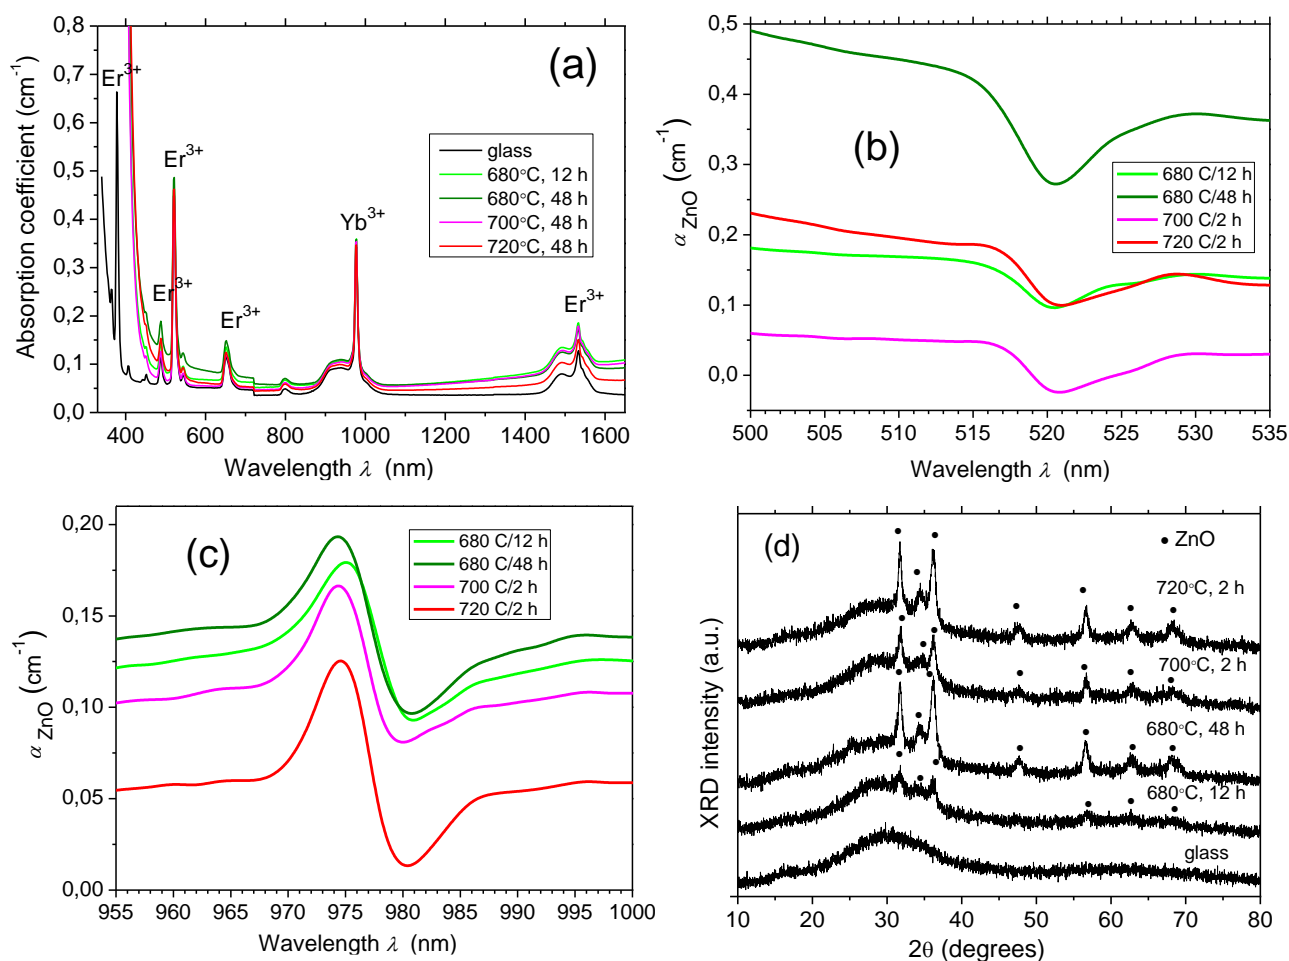




Fig. 1311. Absorption spectra (a), the extinction coefficient  $\alpha_{\text{ZnO}}$  in some spectral ranges around the absorption peaks of  $\text{Er}^{3+}$  ( $\lambda \cong 520 \text{ nm}$ ) (b) and  $\text{Yb}^{3+}$  ( $\lambda \cong 978 \text{ nm}$ ) (c); the corresponding XRD patterns (c) of the initial and heat-treated glasses containing (0.3 mol%  $\text{Er}_2\text{O}_3$  + 0.3 mol%  $\text{Yb}_2\text{O}_3$ ).

The spectra of visible  $\text{Er}^{3+}$  luminescence of the initial glass doped with 0.1/0.1 mol%  $\text{Er}_2\text{O}_3/\text{Yb}_2\text{O}_3$  and glass-ceramics based on ZnO nanocrystals and obtained by its heat-treatments at 700–800 °C were presented in [66]. The excitation wavelength was 488 nm. With the heat-treatment, the luminescence intensity gradually decreased while the shape of the emission bands did not change. This indicates that the  $\text{Er}^{3+}$  ions do not enter into the ZnO nanocrystals and remain in the residual glassy phase until the heat-treatment temperature of at least 800 °C. The observed decrease of the luminescence intensity can be explained by quenching of  $\text{Er}^{3+}$  luminescence in the residual glassy phase which volume decreases with the heat-treatment. The conclusion about location of RE ions in the residual glass is confirmed by the XRD pattern of the glass-ceramic prepared by heat-treatment at 1300 °C for 2 h (Fig. 14). The XRD pattern exhibits diffraction maxima at  $2\theta=28.20^\circ$  and  $28.80^\circ$  with almost similar intensities and a maximum at  $\sim 28.5^\circ$  with a low intensity. Their appearance is connected with crystallization of RE silicate, orthorhombic phase  $(\text{Er},\text{Yb})_2\text{Si}_2\text{O}_7$  (space group: Pna21), which corresponds to the ICDD card No. 82-0732.

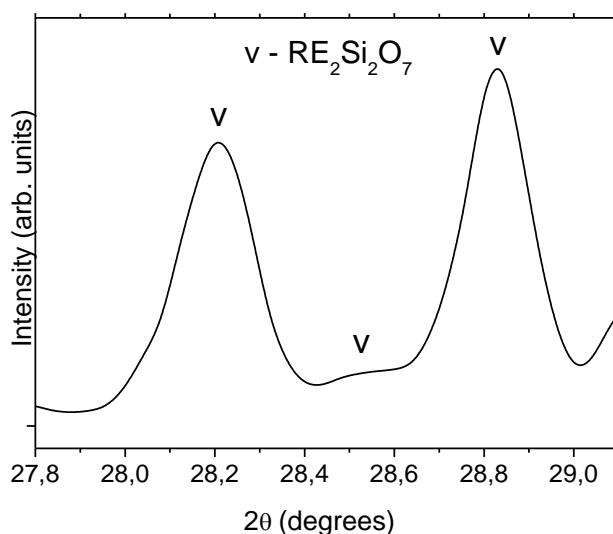


Fig. 1412. The part of XRD pattern of the glass-ceramic doped with 0.1%  $\text{Er}_2\text{O}_3$  and 0.1%  $\text{Yb}_2\text{O}_3$  after heat-treatments at 1300 °C for 2 h recorded in a scanning mode ( $2\theta=27.6\text{--}29.8^\circ$ ) with 100 s exposure time.

## 3.2. Ceramics

### 3.2.1. Ceramics doped with RE ions

#### 3.2.1.1. XRD analysis of ceramics

A typical XRD pattern of RE-doped ZnO ceramic is shown in Figure 15 by an example of the ZnO:5% Er sample. All the XRD patterns of the ZnO:Yb, ZnO:Er and ZnO:(Er, Yb) transparent ceramics evidence crystallization of hexagonal (sp. gr.  $P6_3mc$ ) phase of ZnO with wurtzite structure and  $RE_2O_3$  with a cubic (sp. gr.  $Ia\bar{3}$ ) C-type bixbyite structure. The calculated ZnO unit cell parameters for the ZnO:Yb, ZnO:Er and ZnO:(Er, Yb) ceramics nearly coincide with those for undoped ZnO ( $a = 3.249 \text{ \AA}$ ,  $c = 5.205 \text{ \AA}$ , ISDD card No. 5-0664). They do not change with increasing the RE content from 0.2 to 5 wt%, which indicates that  $RE^{3+}$  ions do not enter the ZnO structure under the conditions used for the manufacture of ceramics (HPing of mechanically mixed powders of reagents at temperatures of 1150 - 1180 °C).

The fragment of the XRD pattern in the range of diffraction angles  $2\theta$  of 29.0 - 30.3° contains intense diffraction peaks of  $Er_2O_3$  and  $Yb_2O_3$  with the Miller's index  $(hkl) = (222)$ , Fig. 16(a). The volume fraction of  $RE_2O_3$  crystals in ceramics gradually increases with RE content, Figure 16(b). The calculated unit cell parameters of  $RE_2O_3$  are independent of the RE content in ceramics. The unit cell parameter of  $Yb_2O_3$   $a = 10.441 \pm 0.003 \text{ \AA}$ , that of  $Er_2O_3$ ,  $a = 10.545 \pm 0.003 \text{ \AA}$ . The size of  $RE_2O_3$  crystals in ZnO:RE ceramics is also independent of the dopant concentration; the average size of  $Yb_2O_3$  crystals is ~70 nm, the average size of  $Er_2O_3$  crystals is ~76 nm.

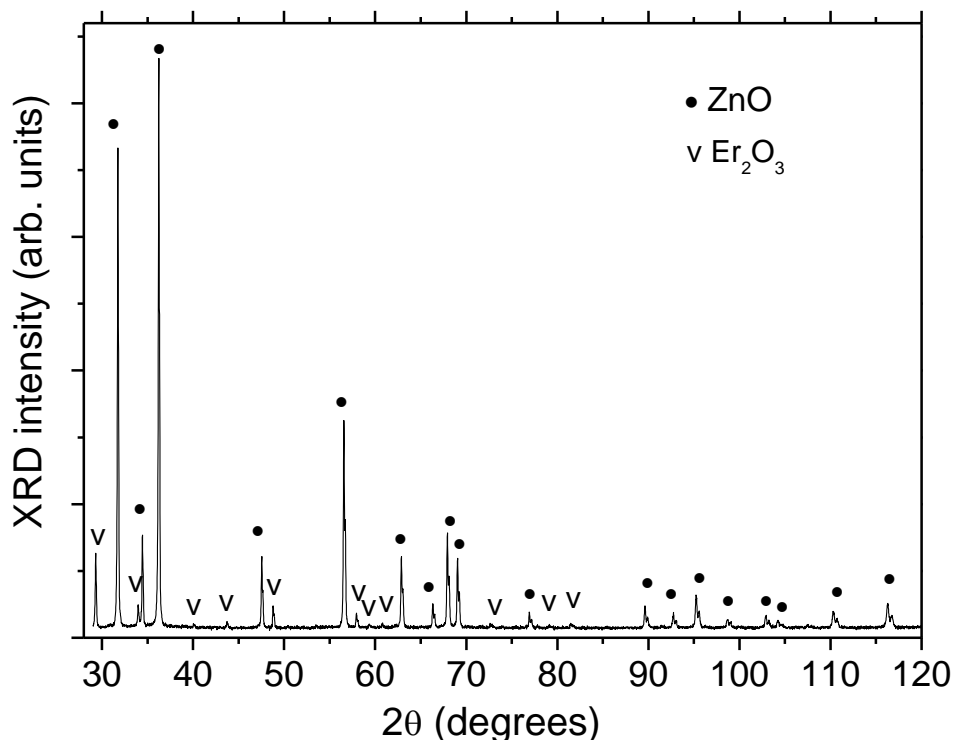


Fig. 1513. XRD pattern of ZnO:5% Er optical ceramic.

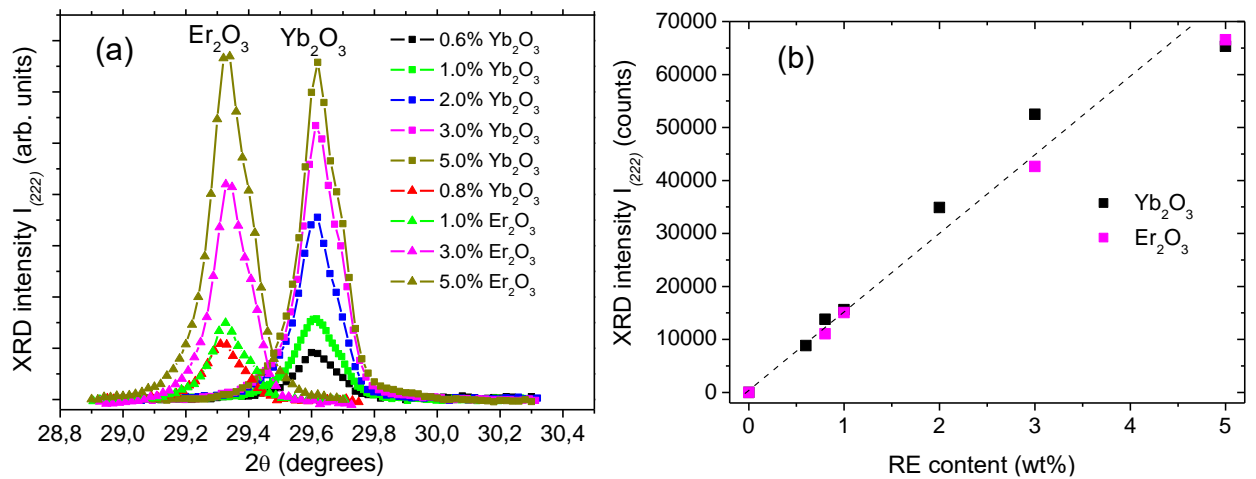


Fig. 1614. (a) XRD patterns of ZnO:RE ceramics with different Er and Yb doping levels in the  $2\theta$  range of 28.9–30.3° corresponding to (222) peaks of  $Er_2O_3$  and  $Yb_2O_3$ ; (b) dependence of the corresponding peak diffraction intensity at  $2\theta$  of 29.33° and 29.63° on the RE content.

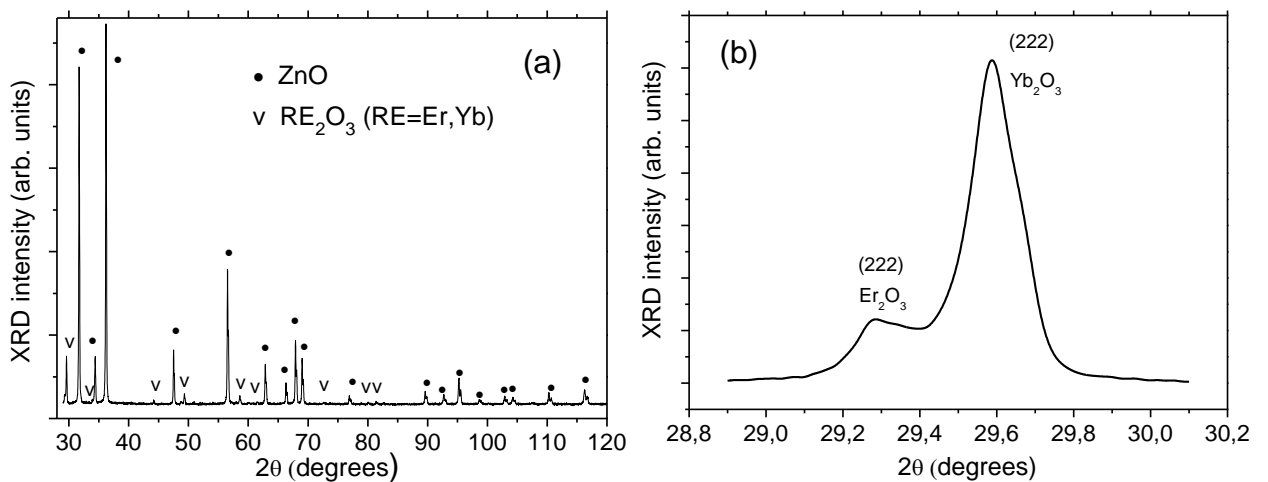


Fig. 1715 (a) XRD pattern of ZnO:1/4 wt% Er/Yb; (b) XRD pattern of ZnO:1% Er/4% Yb ceramic with different Er and Yb doping level in the  $2\theta$  range of 28.9–30.3° corresponding to (222) peaks of  $Er_2O_3$  and  $Yb_2O_3$ .

### 3.2.1.2. Texture characterization of ceramics

The uniaxial pressing conditions used for the manufacturing of ZnO transparent ceramics inevitably result to texture appearance, i.e., in a predominant orientation of crystal grains. The texture coefficient is a parameter that allows estimating the contribution of different planes of ZnO crystals to the texture formation, see Eq. (1). The reflections from the planes of a hexagonal prism have Miller's indices (100) and (110), the reflections from a pedion have the (002) indices, and those from a hexagonal pyramid have the (101) and (102) indices. For the undoped ZnO ceramic, the texture is dominated by the (100) and (110) prism planes of the ZnO crystals [88]. For the ceramics containing RE ions, the prism planes with  $(hkl) = (100)$  and (110) and the shallow

pyramid (101) dominate. These texture changes can be assigned to localization of RE ions on the active faces of the ZnO crystals [89].

### 3.2.1.3. Morphological characterization of ceramics

The surface morphology of ceramics was characterized by SEM, see Fig. 18, that shows typical SEM images of an etched polished surface of the 0.4 wt% Er-doped transparent ZnO ceramic as an example.

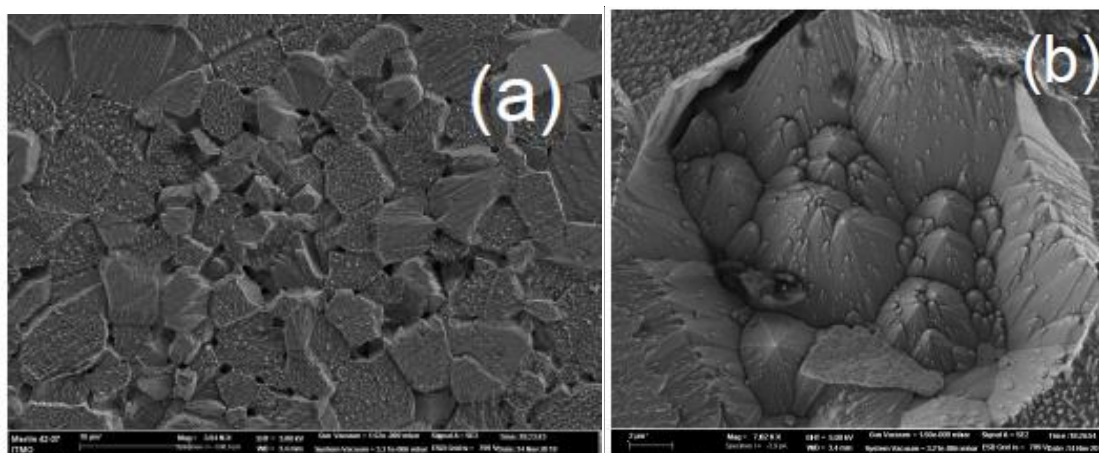


Fig. 1816. SEM images of the polished surface of 0.4 wt% Er-doped ZnO ceramic. The scale bars are (a) 10  $\mu\text{m}$  and (b) 2  $\mu\text{m}$ .

The powder HIPing occurs along thermodynamically favorable crystal planes. The images demonstrate grain surfaces with different orientations. They are the faces of the prism and pedions with characteristic growth hillocks in the form of hexagonal pyramids [89]. The microstructure of the ZnO:0.4 wt% Er ceramic presented in Fig. 18(a,b) is characteristic of all the ceramics under study. The sizes of the resulting grains are not uniform. It is reasonable to assume that larger grains are built of ZnO, while the small grains can be attributed to RE<sub>2</sub>O<sub>3</sub> crystals. The variation of the type of RE element (Er or Yb), its concentration, the source of the RE<sub>2</sub>O<sub>3</sub> reagent and the HIPing temperature do not influence the surface morphology of ZnO:RE crystals. Note that synthetic ZnO single crystals demonstrate similar morphology as the hexagonal prism, the pedion, and the hexagonal pyramid are simple forms characteristic for hexagonal ZnO crystals belonging to the *6mm* point group [11,12]. Located on the crystal faces, and not entering the zinc oxide structure, Er and Yb doping ions have an inhibitory effect on the grain growth of ZnO ceramics. The addition of RE ions significantly, (almost 4 times, from 23.0 to 7  $\mu\text{m}$ ) reduces the average grain size of ZnO ceramics prepared at the same HIPing temperature of 1150 °C [89].

### 3.2.1.4. The microstructure and compositional analysis of the ZnO and ZnO:Er,Yb ceramics

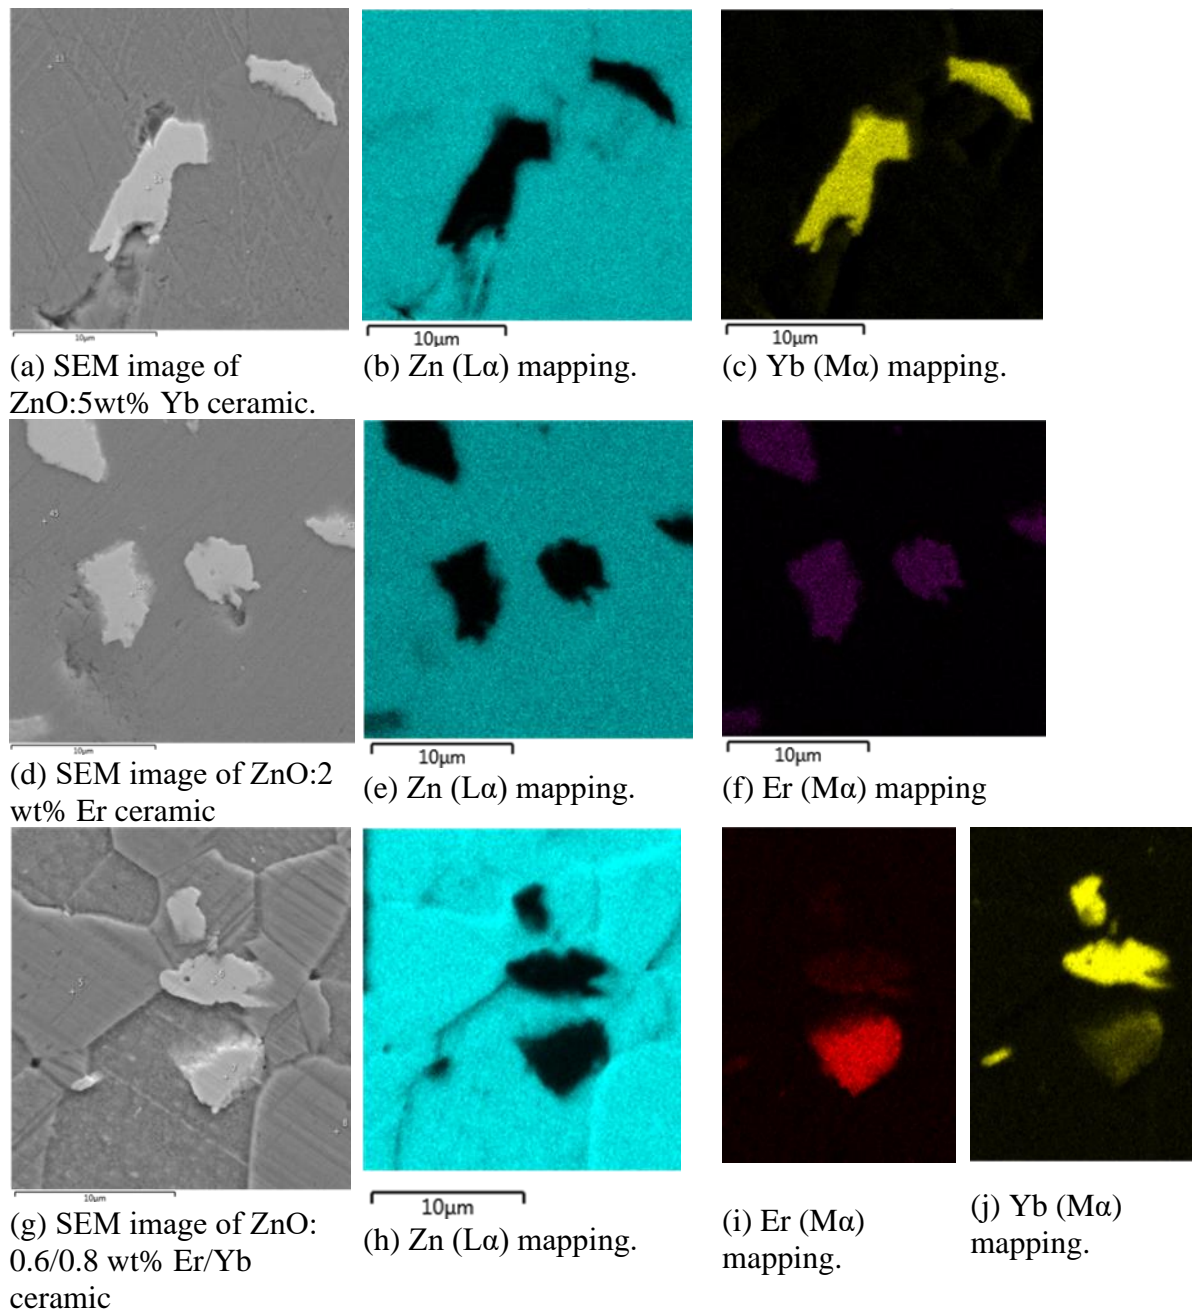


Fig. 1917. (a,d,g) SEM images of the polished and etched surface of the ZnO:RE ceramics; (b,c,e,f,h-j) EDX element mapping of (b,e,h) Zn ( $L\alpha$ ), (c,j) Yb ( $M\alpha$ ) and (f,i) Er ( $M\alpha$ ). (a-c) the ZnO:5Yb ceramic; (d-f) ZnO:2 wt% Er ceramic; (g-j) ZnO:0.6 wt% Er/0.8wt% Yb ceramic.

It has been shown [78,79.] that the efficient energy transfer from ZnO to Yb<sup>3+</sup> ions in the nanocomposites is due to the formation of a tight contact between the Yb<sub>2</sub>O<sub>3</sub> and ZnO nanoparticles (i.e., the Yb<sub>2</sub>O<sub>3</sub>-ZnO heterojunction) and it arises mainly from the quantum cutting mechanism [1].

### 3.2.2. Ceramics doped with cobalt ions

### 3.2.2.1. XRD analysis of ceramics

We made the first attempts to prepare ZnO ceramics doped with cobalt ions. The selected Co concentrations were 0.1, 0.5, 1.0 and 5.0 wt%. A typical XRD pattern is shown in the example of the ZnO:1 wt% Co ceramic, see Fig. 20(a). The pattern demonstrates diffraction peaks corresponding to all the planes of the hexagonal phase of ZnO, ISDD #5-0664, and additional peaks located at  $2\theta = 42.30$ ,  $61.42$ , and  $73.99^\circ$ , see Fig. 18(b,c). These peaks correspond, respectively, to (200), (220), and (311) planes of face-centered cubic CoO, *Fm3m*, JCPDS #78-0431.

Table 2. The unit cell parameters ZnO and CoO crystals in ceramics containing 1.0 wt% CoO

CoO content, wt%	The ZnO unit cell parameters (Å)		The CoO unit cell parameter (Å)
	$a (\pm 0.003)$	$c (\pm 0.003)$	$a (\pm 0.003)$
0.5	3.253	5.204	
1.0	3.251	5.203	4.267
5.0	3.254	5.207	4.267

With increasing the cobalt concentration, the unit cell parameters of ZnO crystals remain near unchanged, and their values practically coincide with those indicated in the literature ( $a = 3.249$  Å,  $c = 5.205$  Å, ISDD card No. 5-0664). The fraction of CoO in ZnO:Co ceramics increases in proportion to the concentration of the Co reagent,  $\text{Co}_3\text{O}_4$ . It is possible to trace the growth of the CoO crystal fraction by an increase of intensity of the diffraction peak located at  $2\theta = 42.30^\circ$  and corresponding to the (200) plane of the CoO crystal. At doping with 0.5 wt% Co, the peak (200) on the XRD pattern is not detected. It appears when the Co content is 1.0 wt%, and it increases in the XRD pattern of ZnO: 5.0 wt% Co ceramic. The CoO unit cell parameter  $a$  in ceramics does not change with increasing the Co doping level, see Table 2. The value of the parameter  $a = 4.267$  Å is similar to that of pure CoO ( $a=4.262$  Å, JCPDS #78-0431) though it is possible to expect the formation of solid solution between CoO and cubic ZnO with the rock salt structure (S.G. *Fm3m*,  $a=4.280$  Å, JCPDS #77-0191).

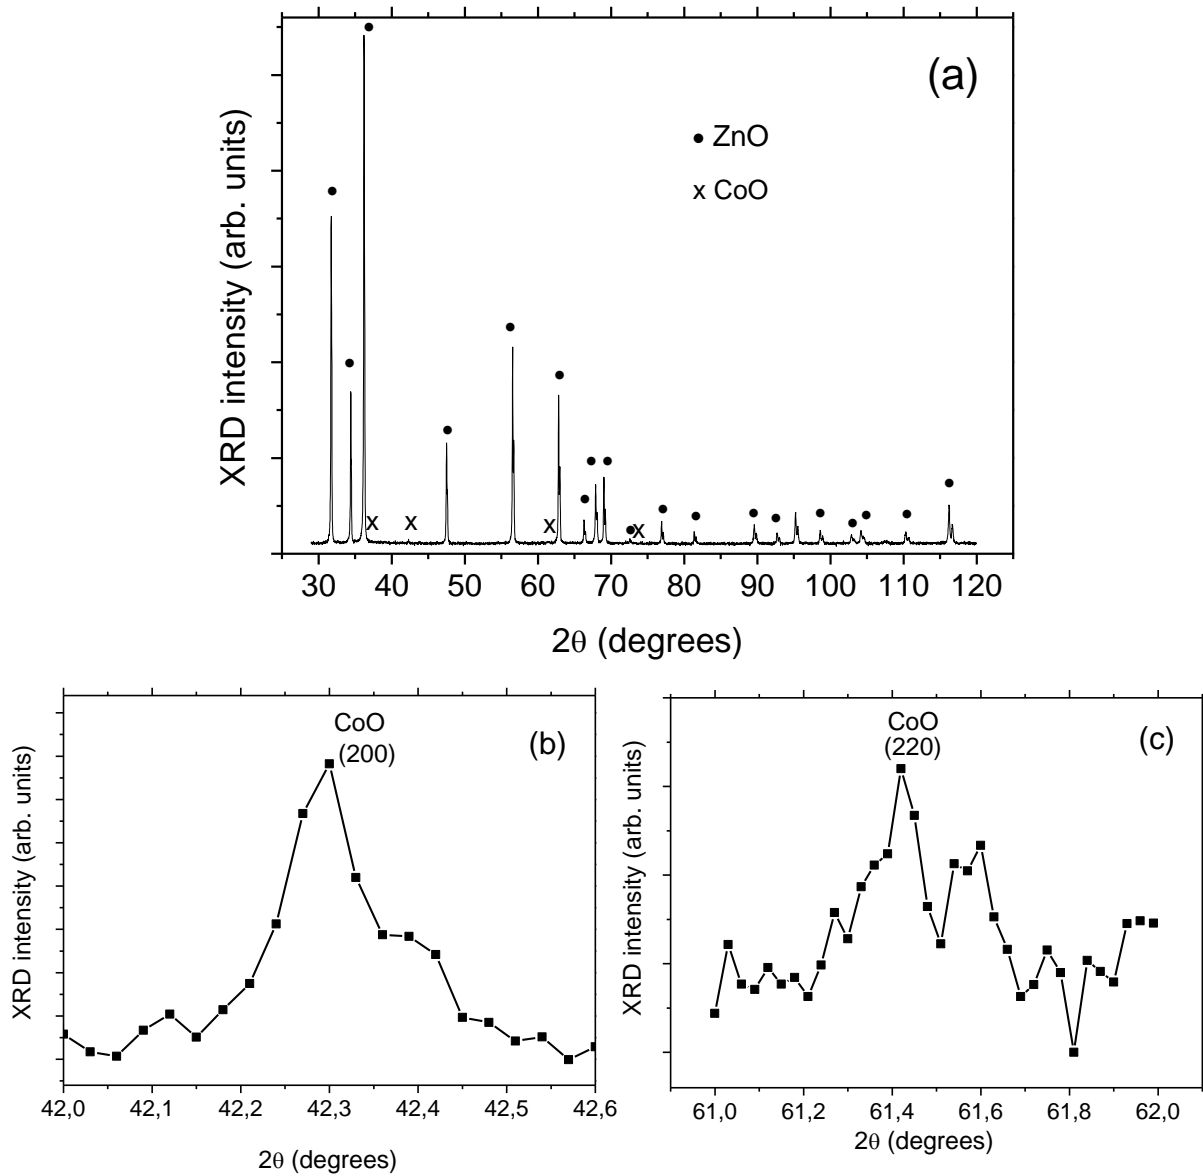


Fig. 2018. (a) XRD pattern of the ZnO: 1 wt% Co ceramic; (b) XRD pattern of ZnO: 1 wt% Co ceramic in the  $2\theta$  range of  $42.0 - 42.6^\circ$  corresponding to the (200) peak of CoO; (c) XRD pattern of ZnO: 1 wt% Co ceramic in the  $2\theta$  range of  $61.0 - 62.0^\circ$  corresponding to the (220) peak of CoO.

### 3.2.2.2. The microstructure and compositional analysis of the ZnO:Co ceramics

The microstructure of ZnO:Co ceramics is composed of grains of various shapes and sizes, see Fig. 21(a) as a typical image. Along with isometric grains, which are characteristic for undoped ZnO ceramic, the grains of rectangular shape are observed. The length of grains somewhat increases with the Co doping level. The grain size varies from 5-7 to 25-30  $\mu\text{m}$ .

Fig. 21(b) presents the backscattered electron image (at low accelerating voltage) of the surface of ZnO:0.5 wt% Co ceramic. The numbers 1-3 mark the dark regions of irregular shape with sizes of 10 to 20  $\mu\text{m}$ . According to SEM-EDX data, these three regions as well as other dark regions not shown here have the same composition and contain ~36 at% Co, 20 at% Zn, and 44



at% O. The composition of the main part of the ceramic was determined in different regions of the sample. The content of Zn and O is found to be near constant when analyzed in different parts of the sample, while the Co content varies from 0.05 to 0.2 at%. For instance, the region denoted by the number 4 has the composition of ~54 at% Zn, ~46% O and contains 0.03 at% Co.

These findings are confirmed by the SEM-EDX element mapping, see Fig. 21(c,d), where two types of cobalt ions localization are observed, i.e., the homogeneous distribution of Co atoms along the ZnO sample as well as their localization within the regions enriched in cobalt ions.

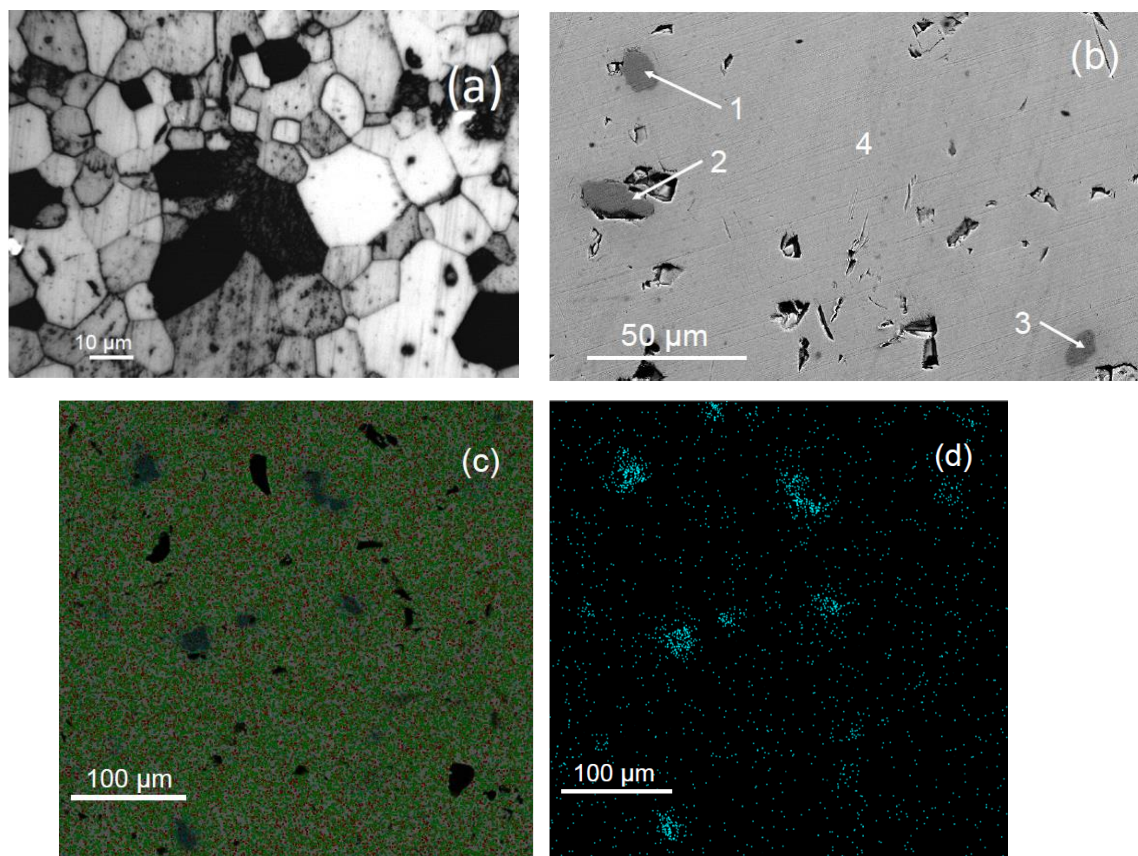


Fig. 2119. (a,b) Micrograph of the etched surface(a) and the backscattered electron image (b) of the ZnO:0.5 wt% Co ceramic; (c,d) EDX Zn, O, and Co element mapping (c) and Co element mapping (d) of the ZnO:1 wt% Co ceramic.

### 3.2.2.3. Optical properties of the ZnO:Co ceramics

Figure 22(a,b) shows the absorption spectra of ZnO:Co ceramics with different doping concentrations. Absorption spectrum of ZnO:1 wt% Co ceramic in the spectral range of 300 – 3300 nm presents the characteristic features of  $\text{Co}^{2+}$  ions and ZnO crystals: there are the broad structured absorption bands of  $\text{Co}^{2+}$  ion in tetrahedral site symmetry position characteristic of these ions in ZnO crystals [74-76], and the absorption band at longer wavelengths ( $\lambda > 1800$  nm) which is connected with the presence of free carriers in semiconductor ZnO crystals [80], see Fig. 22(a).



Figure 22(b) shows that the absorption edge in the spectrum shifts to longer wavelengths, intensities of cobalt absorption bands increase, and the raise of absorption connected with the presence of free carriers shifts to longer wavelengths with the increase of doping concentration. The detailed analysis of the  $\text{Co}^{2+}$  spectrum was done based on the paper of R. Pappalardo *et al.* [74] and refs [75,76]. The dominant absorption bands in the visible spectral range at 566, 610 and

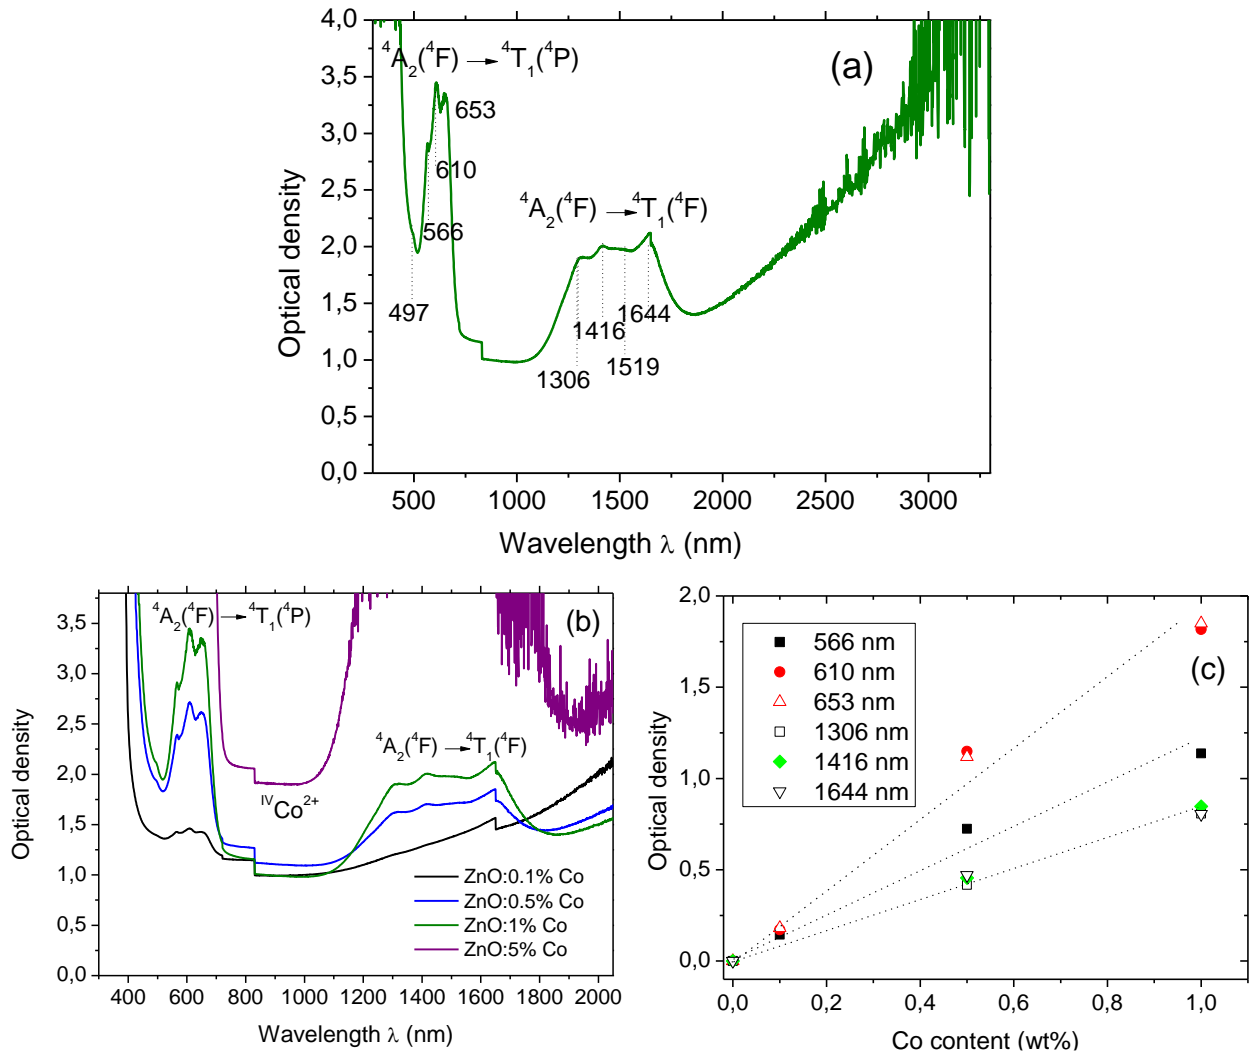


Fig. 2220. Absorption spectrum of ZnO:1 wt% Co ceramic in the spectral range of 300 – 3300 nm (a); absorption spectra of ZnO: Co ceramics doped with 0.1 – 5.0 wt.% Co in the spectral range of 300 – 2050 nm (b); the dependence of the the peak optical density at 566, 610, 653, 1306, 1416, and 1644 nm on the Co content (c). The thickness of the samples is  $\sim 0.5$  mm.

653 nm were assigned as  ${}^4A_2({}^4F) \rightarrow {}^4T_1({}^4P)$  and the bands in the IR at 1306, 1416, 1519, and 1644 nm were assigned as  ${}^4A_2({}^4F) \rightarrow {}^4T_1({}^4F)$  transition due to the high spin  $d^7$  electron configuration of the tetrahedrally coordinated  $\text{Co}^{2+}$  ions. We should bear in mind that according to XRD data presented above, ZnO:Co ceramics contain CoO crystals.  $\text{Co}^{2+}$  ions have octahedral coordination in CoO crystals with the rock salt structure [90]. The absorption spectrum of CoO is presented in

Fig. 5 of ref. [91]. It contains three bands, i.e. the rather narrow band at 357 nm attributed to ligand-metal charge transfer from O(II) to Co(II), the absorption centered at 550 nm and ascribed to Co(II) transitions in octahedral crystal field, and a very broad absorption in the near infrared centered at about 1000 nm and spanning up to 1200 nm. The absorption spectrum of octahedrally coordinated  $\text{Co}^{2+}$  ions in MgO [74] presents absorption bands in the visible and in the near infrared. R. Pappalardo *et al.* mention [74] that “a comparison of the absorption bands of MgO: Co and ZnO: Co shows that the ZnO: Co spectrum is markedly shifted towards lower energies and that the shape of the bands in the infrared region is markedly different for the two systems. On the contrary, the shape of the bands in the visible region of the spectrum does not show the drastic difference. The oscillator strength in tetrahedral coordination (ZnO:Co) is greater by a factor  $\sim 10^3$  than for MgO:Co.” Therefore, absorption caused by  $\text{Co}^{2+}$  ions in octahedrally coordinated CoO crystals come annotated in absorption spectra of ZnO:Co ceramic. According to Figure 20(c), the Beer’s law, i.e., a linear dependence between the concentration of  $\text{Co}^{2+}$  ions and the peak optical density (after subtracting the background losses), is fulfilled for all  $\text{Co}^{2+}$  peaks in the absorption spectra of ceramics. It indicates that with increasing the Co concentration, new species do not appear, which allows us to conclude that the distribution of cobalt ions between the ZnO and CoO crystals is almost independent of the  $\text{Co}^{2+}$  concentration.

### 3.3. Comparison of glass-ceramics and ceramics

In this section, we compare the structure of glass-ceramics and ceramics based on ZnO. Previously, a comparative study of spinel-based ceramics and glass ceramics allowed us to elucidate the structural and spectral features of both materials [92,93].

The XRD pattern of ZnO glass-ceramic doped with 0.1% CoO reveals a multiphase material exhibiting the strongly broadened diffraction peaks of ZnO located at the same positions as for the ZnO ceramic, as well as a halo located at  $2\theta \approx 29^\circ$  due to a high content of the residual potassium aluminosilicate glass, see Fig. 23(a,b). A small ZnO crystal size and relatively low crystallinity fraction become evident in glass-ceramic. ZnO:Co ceramics are two-phase crystalline material, composed of ZnO crystals with a tiny fraction of CoO crystals.

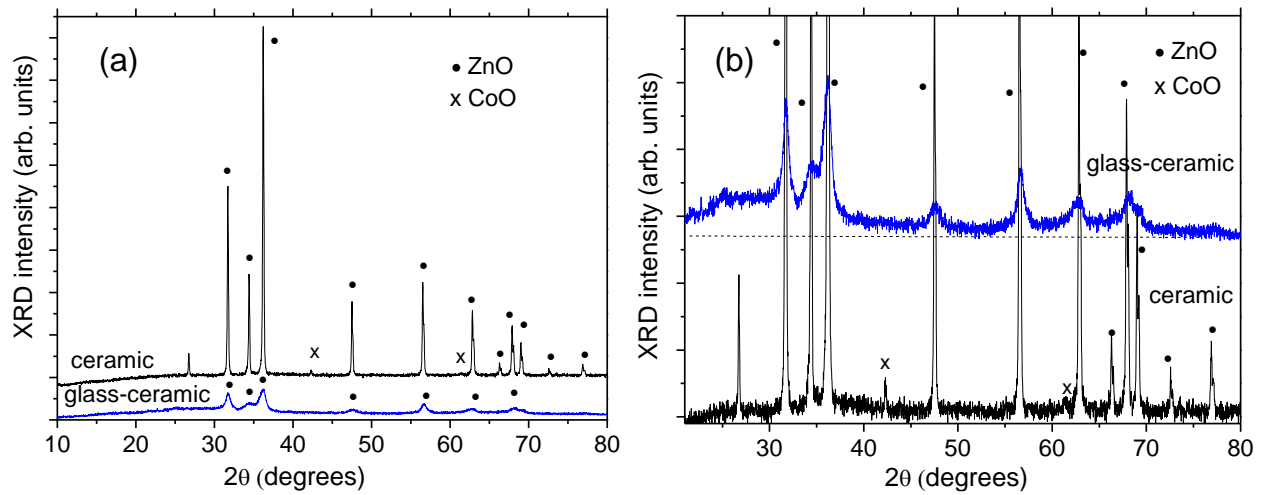


Fig. 231. XRD patterns of the ZnO glass-ceramics doped with 0.1% CoO prepared by the heat-treatment at 750 °C for 2 h and the ZnO:1 wt% Co (a); a close look on the XRD pattern of the ZnO glass-ceramics doped with 0.1% CoO prepared by the heat-treatment at 750 °C for 2 h (b).

The comparison of absorption spectra of cobalt-doped glass-ceramic and ceramic, Fig. 24, clearly indicates the presence of cobalt ions in one oxidation state,  $\text{Co}^{2+}$ , in the  $T_d$  (tetrahedral) sites. The shape of absorption bands and positions of absorption peaks caused by  $\text{Co}^{2+}$  ions in both materials coincide which implies that they both originate from  $T_d$  coordinated  $\text{Co}^{2+}$  ions in  $\text{Zn}^{2+}$  sites in ZnO crystals. The optical losses in the mid IR spectral range in these materials have different origin: in glass-ceramic, the broad band with a maximum at about  $2800\text{ cm}^{-1}$  is due to absorption of OH-groups dissolved in the glass melt; in ceramic the IR absorption is related to the presence of free carriers in semiconductor ZnO nanocrystals. Quite predictably, the transparency of nanophase glass-ceramic is much higher than that of ceramic.

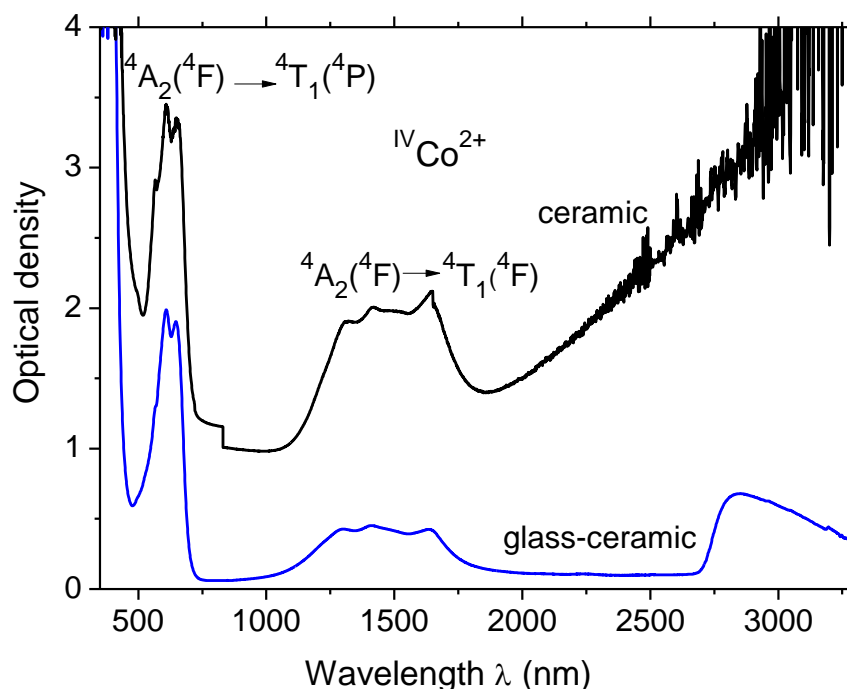


Fig. 242. Absorption spectra of the Zn1 glass-ceramics doped with 0.1% CoO prepared by the heat-treatment at 750 °C for 2 h and the ZnO:1 wt% Co ceramic. The thickness of the glass-ceramic sample is 3 mm, that of ceramic sample is 0.5 mm.

The Raman spectra of the Zn2 glass-ceramics doped with 0.1 mol% Yb<sub>2</sub>O<sub>3</sub> prepared by the heat-treatment at 750 °C for 2 h and of the ZnO:0.2 wt% Yb ceramic presented in Fig. 25 allowed us to reveal the characteristic features of both materials. In this comparison, we based on our interpretations of Raman spectra of glass-ceramics [66] and ceramics [89]. All characteristic vibrations of ZnO with wurtzite structure are observed in the Raman spectra of ZnO:0.2Yb ceramics at 99, 202, 331, ~379, 409, 437, 482, 539, 578, 663, 723, 743, 776, 812, 980, 1104 and 1150 cm<sup>-1</sup>. Their assignment is presented in Table 2 of ref. [89]. Here we only mention that one of the most intense modes in the Raman spectrum of ZnO is a very narrow peak E<sub>2</sub><sup>low</sup> at ~100 cm<sup>-1</sup>, ascribed to vibrations of the zinc sublattice in ZnO [94], while another intense Raman mode E<sub>2</sub><sup>high</sup> at ~437 cm<sup>-1</sup> is assigned to oxygen vibrations [94].

In the Raman spectrum of glass-ceramic previously we noticed only the most intense ZnO Raman modes. Now we can confirm that other modes are also found in the Raman spectrum of glass-ceramic. The most interesting finding is that the broad ZnO Raman modes at 1104 and 1150 cm<sup>-1</sup> do exist in the spectrum of glass-ceramic. Indeed, the broad band with the maximum at 1104 nm is a result of superposition of vibrations within the aluminosilicate residual glass and the 2A<sub>1</sub>(LO), 2E<sub>1</sub>(LO) and 2LO modes of ZnO. The broad intense peaks at 482 and 578 cm<sup>-1</sup> in the spectrum of glass-ceramic are assigned to vibrations within the aluminosilicate residual glass, though the weak modes of ZnO can also participate in these bands. Comparison of Raman spectra of glass-ceramics and ceramics elucidates the difference in phase compositions of the materials and allows to notice those Raman modes of ZnO crystals in the Raman spectrum that could not be found without this comparison.

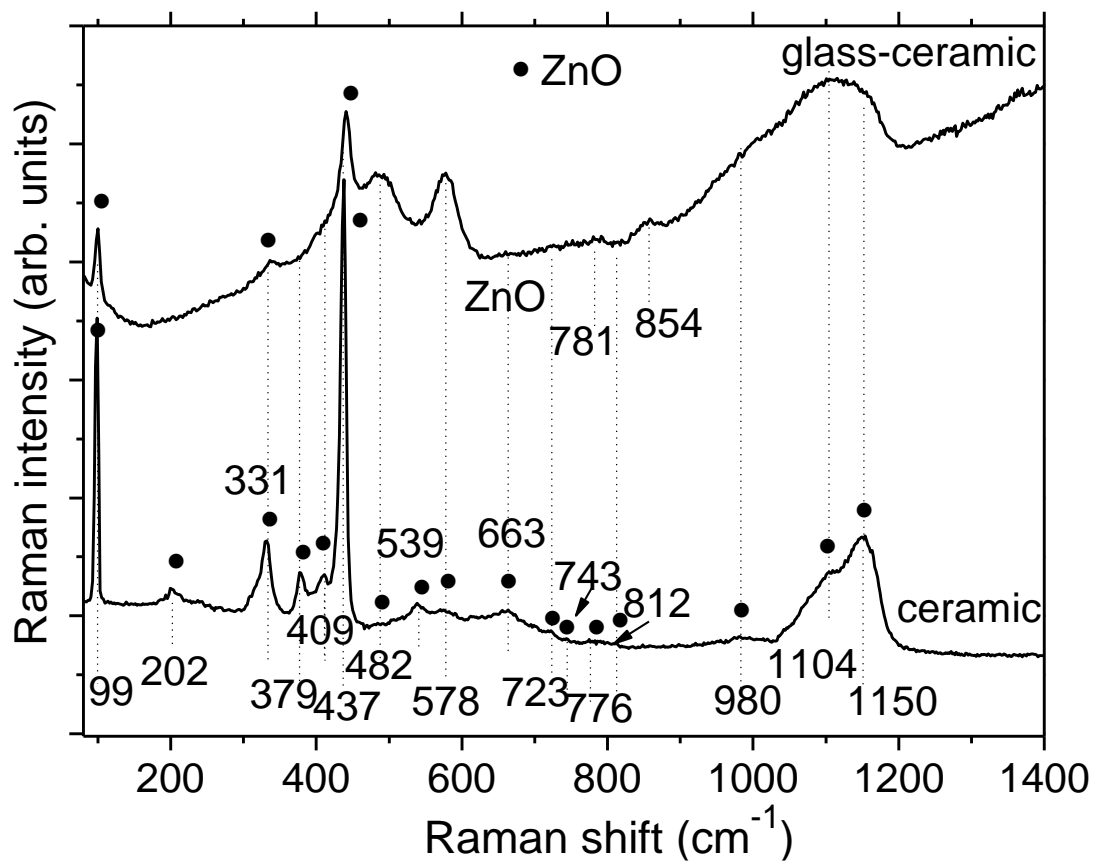
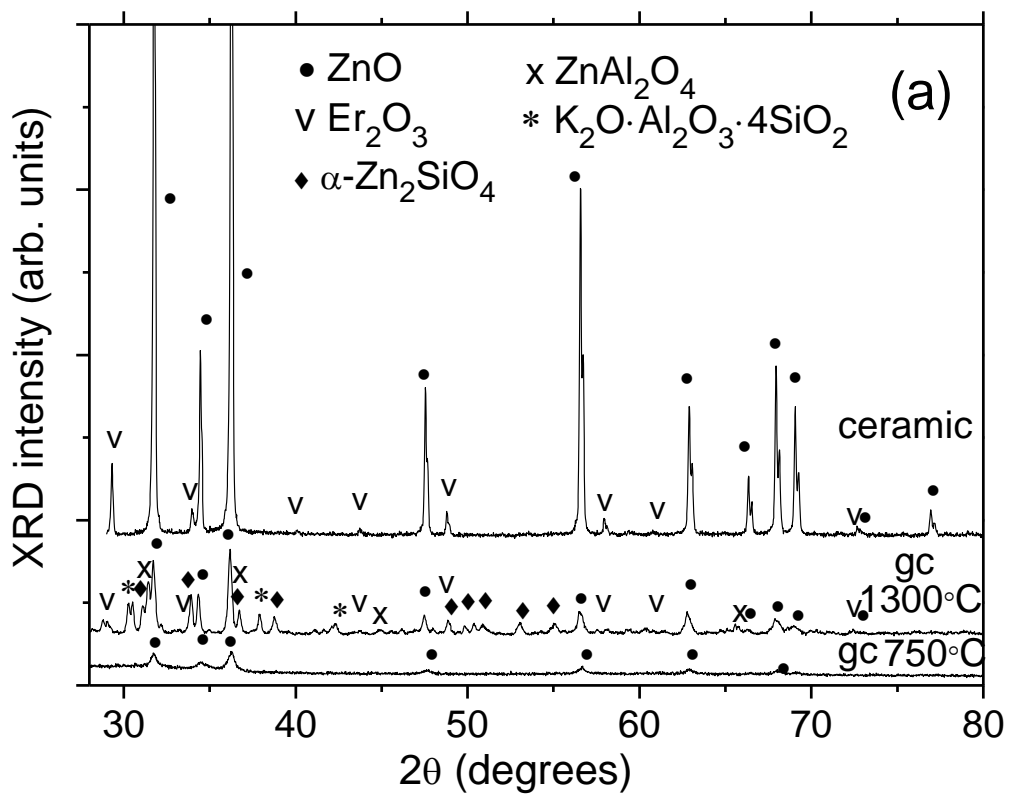


Fig. 25. Raman spectra of the ZnO glass-ceramics doped with 0.1 mol%  $\text{Yb}_2\text{O}_3$  prepared by the heat-treatment at 750 °C for 2 h and of the ZnO:0.2 wt% Yb ceramic.



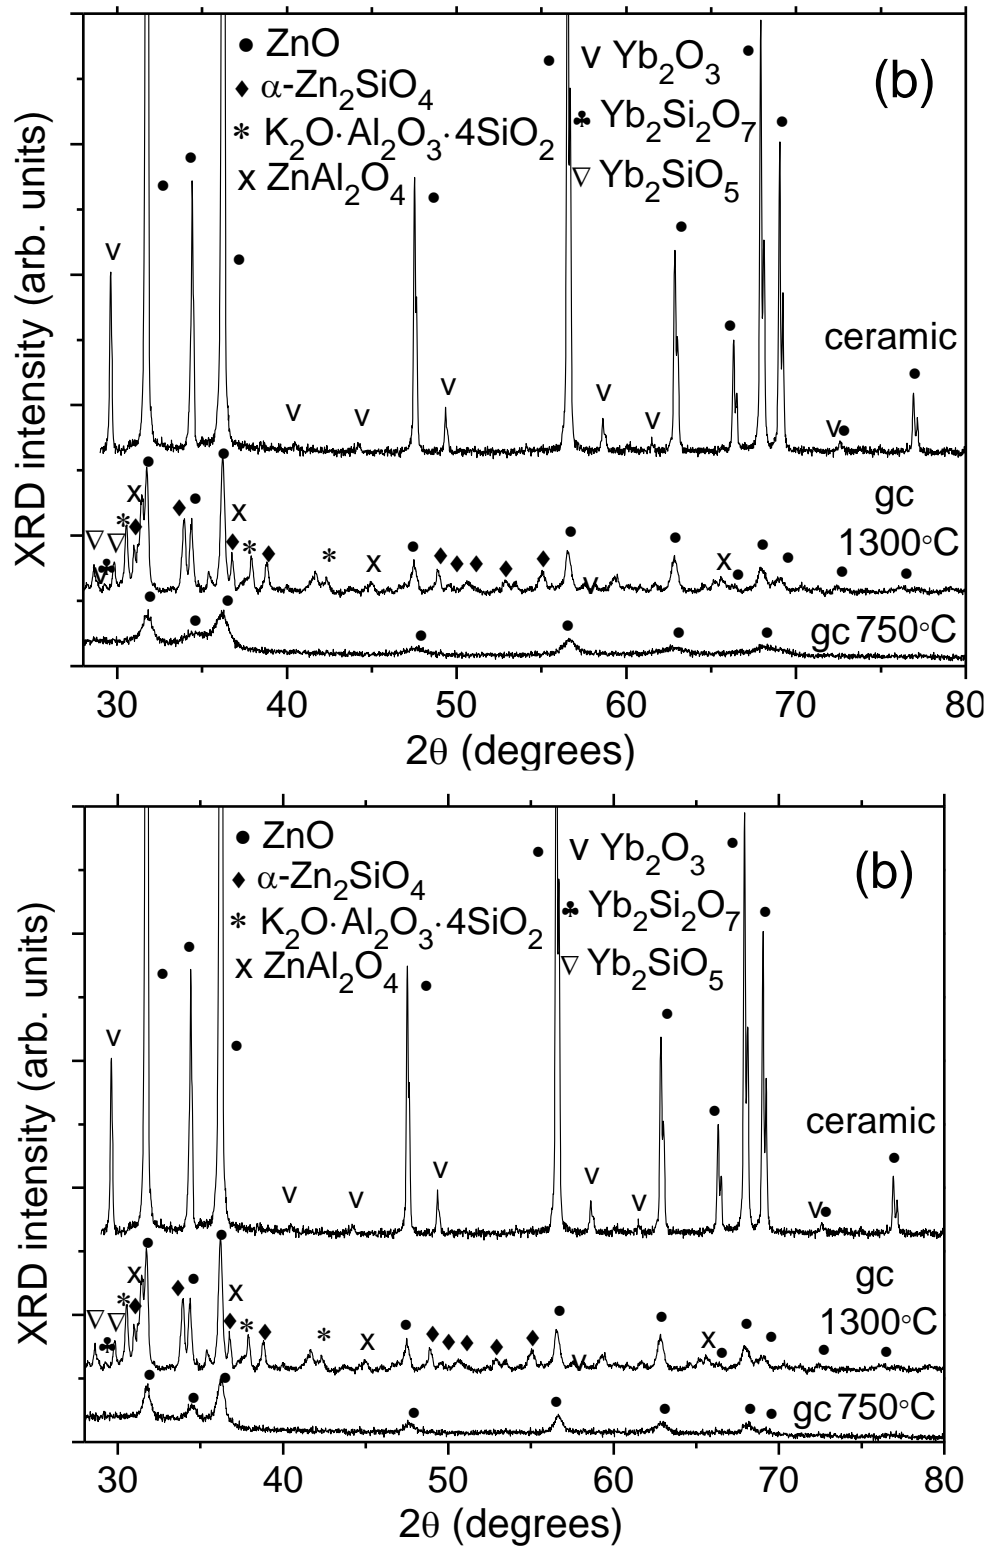


Fig. 26. XRD patterns (a) of the Zn2 glass-ceramics doped with 1.5 mol%  $\text{Er}_2\text{O}_3$  prepared by heat-treatments at 750 °C for 2 h and at 1300 °C for 2 h and of the ZnO:3 wt% Er ceramic; (b) of the Zn2 glass-ceramics doped with 1.5 mol%  $\text{Yb}_2\text{O}_3$  prepared by heat-treatments at 750 °C for 2 h and at 1300 °C for 2 h and of the ZnO:3 wt% Yb ceramic

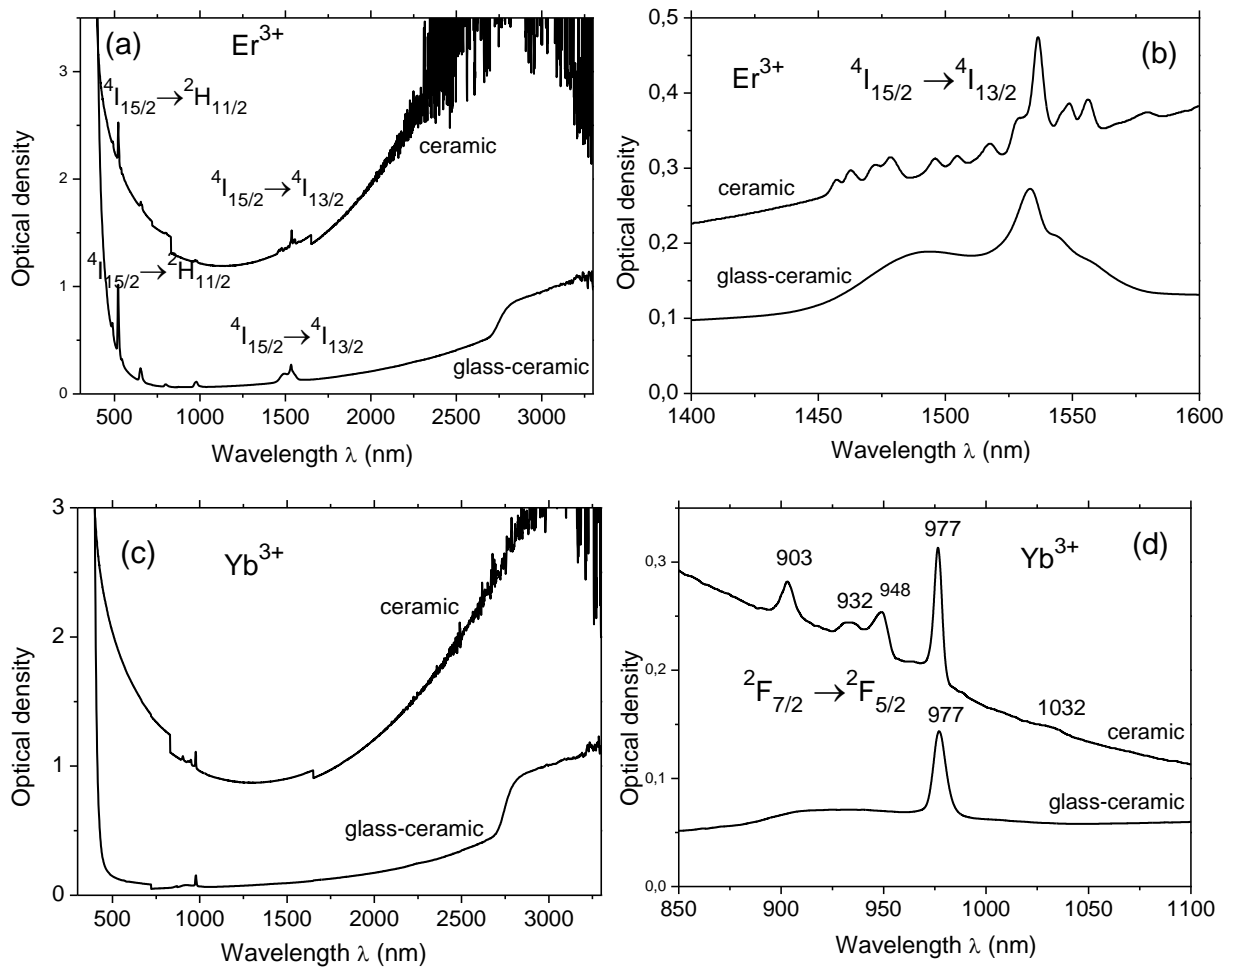


Fig. 27. (a,b) Absorption spectra of the Zn2 glass-ceramics doped with 1.5 mol%  $\text{Er}_2\text{O}_3$  prepared by the heat-treatment at 750 °C for 2 h and the ZnO:3 wt% Er ceramic in the spectral range of 300 – 3300 nm (a); in the spectral range of 1400 – 1600 nm (b). The thickness of the glass-ceramic sample is 1 mm, that of the ceramic sample is 0.5 mm. (c,d) Absorption spectra of the Zn2 glass-ceramics doped with 0.1 mol%  $\text{Yb}_2\text{O}_3$  prepared by the heat-treatment at 680 °C for 48 h and the ZnO:3 wt% Yb ceramic in the spectral range of 300 – 3300 nm (c); in the spectral range of 850 – 1100 nm (d). The thickness of the glass-ceramic sample is 3 mm, that of the ceramic sample is 0.5 mm.

Different origin of absorption peaks in spectra of glass-ceramics and ceramics doped with RE ions is revealed by the comparison of XRD patterns and absorption peaks of Yb and Er-containing materials. Absorption spectra of ZnO:Yb and ZnO:Er ceramics are characteristic of corresponding RE oxides and demonstrate well-reserved multiplets. The broad peaks of RE ions in spectra of glass-ceramic reflect their location in the residual glass phase.

## Conclusions

The structure and phase transformations in ZnO: glass-ceramics and optical ceramics doped with rare-earth and transition-metal ions were studied by small angle X-ray scattering, differential scanning calorimetry, X-ray diffraction analysis, transmission electron microscopy, and Raman spectroscopy. Morphology of the fracture surface of ceramics was characterized by scanning electron microscopy in combination with energy dispersive X-ray analysis. Absorption spectra of the materials were recorded.

In the course of the glass-ceramics development, it was revealed that during the initial glass casting and cooling, regions of structural inhomogeneity of various types are formed, depending on the type and concentration of the TM and RE ion. The character of the primary phase decomposition, which depends on the type and concentration of TM and RE ion, determines the kinetics of crystallization of ZnO and the time - temperature ranges of transformations of Zn-containing phases  $\text{ZnO} \rightarrow \beta\text{-willemite} (\beta\text{-Zn}_2\text{SiO}_4) \rightarrow \alpha\text{-willemite} (\alpha\text{-Zn}_2\text{SiO}_4) \rightarrow \text{ZnO} + \text{ZnAl}_2\text{O}_4$ , observed with an increase in the heat-treatment temperature in the range of 680–1200 °C.

In glass-ceramics, TM ions enter the ZnO and willemite nanocrystals while RE ions do not enter the structure of ZnO crystals, but are located both on the surface of these crystals and in the volume of the residual glass. As a result of high-temperature treatment, RE ions form their own phase of RE silicates. In the case of high concentrations of RE ions, RE<sub>2</sub>O<sub>3</sub> crystals are formed along with RE silicates.

The spectral-luminescent properties of transparent ZnO-based glass-ceramics are determined by the properties of both ZnO crystals and rare-earth ions. Glass-ceramics prepared by heat-treatments at up to 900 °C are transparent and contain either ZnO or a mixture of ZnO and  $\beta$ -willemite nanocrystals.

It was found that in optical ceramics, Co<sup>2+</sup> ions enter the structure of ZnO crystals while RE ions do not enter their structure, but are located both on the surface of the crystals and form their own phase of RE<sub>2</sub>O<sub>3</sub>. The RE oxide crystallinity fraction increases in proportion with the RE ion doping level. Thus, ZnO optical ceramics doped with RE ions cannot be considered single-phase materials. Addition of RE ions leads to a significant decrease in the average size of ZnO crystals in ceramics from 40 to 5-15  $\mu\text{m}$ . The texture characteristics of ZnO ceramics are changes with addition of RE ions, which implies modification of the surface of ZnO particles due to selective location of RE ions on certain grain boundaries.

The development of nanosized transparent glass-ceramics and optical ceramics based on ZnO crystals doped with transition metal and rare earth ions is important for photonics and optoelectronics. The preparation of these materials by the melt-quenching technique with controlled crystallization and by the recrystallization during the uniaxial hot-pressing is not only



much cheaper and technologically advanced than the growth of single crystals, but also provides high uniformity of properties for relatively large-sized products made of these materials.

The results obtained will be used in the development of novel transparent optical ceramics and glass-ceramics based on ZnO doped with RE and TM ions and characterized by low scattering losses, high luminescence efficiency and promising for a wide range of optoelectronic devices.

### **Acknowledgements**

This work was partly supported by the RFBR (Grant 19-03-00855).

## References

1. M. S. Ramachandra Rao, Tatsuo Okada, ZnO Nanocrystals and Allied Materials, Springer India 2014, 1-374, ISSN 0933-033X ISSN 2196-2812 (electronic), ISBN 978-81-322-1159-4 ISBN 978-81-322-1160-0 (eBook), <https://doi.org/10.1007/978-81-322-1160-0>.
2. D. Daksh, Y.K. Agrawal, Rare earth-doped zinc oxide nanostructures: a review, *Rev. Nanosci. Nanotechnol.* 5 (2016) 1–27. <https://doi.org/10.1166/rnn.2016.1071>.
3. U. Orgur, Ya.I. Alivov, C. Liu, A. Teke, M.A. Reshnikov, S. Dogan, V. Avrutin, S.- J. Cho, H. Morkoc, A comprehensive review of ZnO materials and devices, *J. Appl. Phys.* 98 (2005), <https://doi.org/10.1063/1.1992666>, 041301-1-103.
4. L. Schmidt-Mende, J.L. MacManus-Driscoll, ZnO – nanostructures, defects, and devices, *Mater. Today*, 10 (5) (2007) 40-48, [https://doi.org/10.1016/S1369-7021\(07\)70078-0](https://doi.org/10.1016/S1369-7021(07)70078-0).
5. C. Klingshirn, J. Fallert, H. Zhou, J. Sartor, C. Thiele, F. Maier-Flaig, D. Schneider, H. Kalt, 65 years of ZnO research – old and very recent results, *Phys. Status Solidi B* 247 (2010) 1424–1447, <https://doi.org/10.1002/pssb.200983195>.
6. P.A. Rodnyi, I.V. Khodyuk, Optical and luminescence properties of zinc oxide, *Opt. Spectrosc.* 111 (2011) 776–785, <https://doi.org/10.1134/S0030400X11120216>.
7. B.K. Meyer, H. Alves, D.M. Hofmann, W. Kriegseis, D. Forster, F. Bertram, J. Christen, A. Hoffmann, M. Straßburg, M. Dworzak, U. Habocek, A.V. Rodina, Bound exciton and donor–acceptor pair recombinations in ZnO, *Phys. Status Solidi B* 241 (2004) 231–260, <https://doi.org/10.1002/pssb.200301962>.
- 8 7. F. Rahman, Zinc oxide light-emitting diodes: a review, *Opt. Eng.* 58(1) (2019) 10901(1-20), <https://doi.org/10.1117/1.OE.58.1.010901>.
- 9 8. J Theerthagiri, S. Salla, R.A. Senthil, P. Nithyadharseni, A. Madankumar, P. Arunachalam, T. Maiyalagan, H.-S. Kim, A review on ZnO nanostructured materials: energy, environmental and biological applications, *Nanotechnology* 30 (2019) 392001(1-27), <https://doi.org/10.1088/1361-6528/ab268a>.
- 10 9. A. Kołodziejczak-Radzimska, T. Jesionowski, Zinc Oxide—From Synthesis to Application: A Review. *Materials*. 7(4). (2014) 2833-2881, <https://doi.org/10.3390/ma7042833>.
- 11 10. A. Sirelkhatim, S. Mahmud, A. Seenii, N.H.M. Kaus, L.C. Ann, S.K.M. Bakhori, H. Hasan, D. Mohamad, Review on zinc oxide nanoparticles: antibacterial activity and toxicity mechanism, *Nano-Micro Lett.* 7 (2015) 219–242, <https://doi.org/10.1007/s40820-015-0040-x>.
- 12 11. E.V. Kortounova, V.I. Lyutin, V.D. Dubovskaya, P.P. Chvanski, The growth of zinc oxide crystals with impurities, *High Press. Res.* 20 (1–6) (2001) 175–183, <https://doi.org/10.1080/08957950108206165>.

- 13 12. L.N. Demianets, D.V. Kostomarov, I.P. Kuz'mina, S.V. Pushko, Mechanism of growth of ZnO single crystals, *Crystallogr. Rep.* 47 (2002) S86–S98, <https://doi.org/10.1134/1.1529962>.
- 14 13. V.A. Demidenko, E.I. Gorokhova, I.V. Khodyuk, O.A. Khristicha, S.B. Mikhrin, P.A. Rodnyi, Scintillation properties of ceramics based on zinc oxide, *Radiat. Meas.* 42 (2007) 549 – 552, <https://doi.org/10.1016/j.radmeas.2007.01.050>.
- 15 14. J.S. Neal, D.M. DeVito, B.L. Armstrong, M. Hong, B. Kesanli, X. Yang, N.C. Giles, J. Y. Howe, J.O. Ramey, D.J. Wisniewski, M. Wisniewska, Z.A. Munir, L.A. Boatner, Investigation of ZnO-based polycrystalline ceramic scintillators for use as  $\alpha$ -particle detectors, *IEEE Trans. Nucl. Sci.* 56 (2009) 892–898, <https://doi.org/10.1109/TNS.2008.2004702>.
- 16 15. M. Hohg, D. Fredrick, X. Yang, J.S. Neal, Z.A. Munir, Characterization of green-emitting translucent zinc oxide ceramics prepared via spark plasma sintering, *Int. J. Appl. Ceram. Technol.* 8 (2011) 725–733, <https://doi.org/10.1111/j.1744-7402.2010.02527.x>.
- 17 16. E.I. Gorokhova, P.A. Rodnyi, E.P. Lokshin, K.P. Lott, G.B. Kunshina, K. A. Chernenko, G.V. Ananieva, S.B. Eron'ko, I.V. Khodyuk, O.G. Gromov, E. A. Oreschenko, Structural, optical, and scintillation characteristics of ZnO ceramics, *J. Opt. Technol.* 78 (2011) 753–760, <https://doi.org/10.1364/JOT.78.000753>.
- 18 17. M. Prakasamn, O. Viraphong, D. Michau, A. Largeteau, Critical parameters to obtain Yb<sup>3+</sup> doped Lu<sub>2</sub>O<sub>3</sub> and ZnO transparent ceramics, *Ceram. Intern.* 40 (2014) 1859–1864, <https://doi.org/10.1016/j.ceramint.2013.07.088>.
- 19 18. G. Chen, M. Nikl, N. Solovieva, A. Beitlerova, J. Rao, Y. Yang, Y. Zhang, X. Jiang, C. Zhu, Photoluminescent properties of nanocrystallized zinc borosilicate glasses, *Radiat. Meas.* 38 (2004) 771–774, doi:10.1016/j.radmeas.2003.12.010.
- 20 19. M. Nikl, J. Pejchal, R. Jinhua, J. Zhang, G. Chen, A. Beitlerova, A. Yoshikawa, T. Fukuda, Photoluminescence of ZnO-aggregates in oxide glasses. *Opt. Mater.* (2007). 29(5), 552–555, <https://doi.org/10.1016/j.optmat.2005.08.051>.
- 21 20. L. Ding, Y. Yang, X. Jiang, C. Zhu, G. Chen, Photoluminescence of undoped and B-doped ZnO in silicate glasses, *J. Non-Cryst. Solids* 354 (2008) 1382–1385, <https://doi.org/10.1016/j.jnoncrysol.2006.10.088>.
- 22 21. G. Qian, X. Liang, J. Bei, S. Yuan, G. Chen, Photoluminescence properties of zinc oxide in barium and fluorine silicate glasses, *J. Am. Ceram. Soc.*, 90(4) (2007) 1255–1257, <https://doi.org/10.1111/j.1551-2916.2007.01594.x>.
- 23 22. M. Cai, W. Mao, L. Calvez, J. Rocherulle, H. Ma, R. Lebullenger, X. Zhang, S. Xu, J. Zhang, Broadband blue emission from ZnO amorphous nanodomains in zinc phosphate oxynitride glass, *Opt. Lett.* 43(23) (2018) 5845–5848 <https://doi.org/10.1364/OL.43.005845>.

- 24 23. H. Masai, T. Toda, T. Ueno, Y. Takahashi, T. Fujiwara, ZnO glass-ceramics: An alternative way to produce semiconductor materials, *Appl. Phys. Lett.* 94 (2009) 151908(1-3), <https://doi.org/10.1063/1.3120282>.
- 25 24. H. Masai, T. Ueno, T. Toda, Y. Takahashi, T. Fujiwara, Processing and photoluminescence properties of surface crystallized ZnO glass-ceramics, *J. Non-Cryst. Solids*, 356 (52–54) (2010) 3080-3084, <https://doi.org/10.1016/j.jnoncrysol.2010.04.055>.
- 26 25. H. Masai, T. Ueno, Y. Takahashi, T. Fujiwara, Precipitation of ZnO in Al<sub>2</sub>O<sub>3</sub>-doped zinc borate glass ceramics, *Opt. Mater.* 33 (12) (2011) 1980-1983, <https://doi.org/10.1016/j.optmat.2011.03.051>.
- 27 26. H. Masai, T. Ueno, Y. Takahashi, T. Fujiwara, Correlation between surface-crystallized ZnO and the amount of Al<sub>2</sub>O<sub>3</sub> in borate-based glass-ceramics, *J. Amer. Ceram. Soc.* 94(8) (2011) 2452-2457, <https://doi.org/10.1111/j.1551-2916.2011.04604.x>.
- 28 27. Y. Takahashi, M. Kinoshita, T. Miyazaki, M. Osada, N. Terakado, T. Fujiwara, Affects of supercooled liquid state on the properties of the crystallized phase: Microscopic and spectroscopic observations in ZnO-crystallized glass-ceramics, *Appl. Phys. Lett.* 107 (2015) 061902(1-4), <https://doi.org/10.1063/1.4928538>.
- 29 28. L. Yang, X. Wang, Z. Li, P. Liu, F. Liu, S. Ge, F. Song, B. Liu, Y. Shi, R. Zhang, (Er, Yb)-co-doped multifunctional ZnO transparent hybrid materials: fabrication, luminescent and magnetic properties, *J. Phys. D: Appl. Phys.* 44 (2011) 155404(1-5), <https://doi.org/10.1088/0022-3727/44/15/155404>.
- 30 29. G. Singh, S. Kumar, V.P. Singh, R. Vaish, Transparent ZnO crystallized glass ceramics for photocatalytic and antibacterial applications, *J. Appl. Phys.* 125(17) (2019) 175102, <https://doi.org/10.1063/1.5081988>.
- 31 30. Z. Khalkhali, Z. Hamnabard, S.S.A. Qazvini, S. Baghshahi, A. Maghsoudipour, Preparation, phase formation and photoluminescence properties of ZnO–SiO<sub>2</sub>–B<sub>2</sub>O<sub>3</sub> glasses with different ZnO/B<sub>2</sub>O<sub>3</sub> ratios, *Opt. Mater.* 34 (5) (2012) P. 850-855, <https://doi.org/10.1016/j.optmat.2011.11.020>.
- 32 31. A. Bahadur, Y. Dwivedi, S.B. Rai, Structural and spectroscopic diagnosis of Eu:ZnO and Eu:Yb:ZnO glass and ceramics, *Spectrochim. Acta A Mol. Biomol. Spectrosc.* 91 (2012) 217-221, <https://doi.org/10.1016/j.saa.2012.01.073>.
- 33 32. O.M. Ntwaeaborwa, P.H. Holloway, Enhanced photoluminescence of Ce<sup>3+</sup> induced by an energy transfer from ZnO nanoparticles encapsulated in SiO<sub>2</sub>, *Nanotechnol* 16 (2005) 865–868, <https://iopscience.iop.org/article/10.1088/0957-4484/16/6/042>.

- 34 33. J. Bang, H. Yang, P.H. Holloway, Enhanced luminescence of  $\text{SiO}_2 : \text{Eu}^{3+}$  by energy transfer from ZnO nanoparticles, *J. Chem. Phys.* 123 (2005), 084709(1-5), <https://doi.org/10.1063/1.2007647>.
- 35 34. Y. Yu, D. Chen, P. Huang, H. Lin, Y. Wang, Structure and luminescence of  $\text{Eu}^{3+}$  doped glass ceramics embedding ZnO quantum dots, *Ceram. Int.* 36 (3) (2010) 1091-1094, <https://doi.org/10.1016/j.ceramint.2009.12.007>.
- 36 35. F. Xiao, R. Chen, Y.Q. Shen, Z.L. Dong, H.H. Wang, Q.Y. Zhang, H. D. Sun, Efficient energy transfer and enhanced infrared emission in Er-doped ZnO-SiO<sub>2</sub> composites, *J. Phys. Chem. C* 2012, 116, 13458–13462, <https://doi.org/10.1021/jp304075g>.
- 37 36. Y. Dimitriev, R. Iordanova, M. Milanova, A. Bachvarova-Nedelcheva, M. Hassan, M. Abdallah, *Phys. Chem. Glas. Eur. J. Glass Sci. Technol. B* 53 (2012) 254-563, ISSN 00319090.
- 37 37. R. Nagai, T. Honma, T. Komatsu, Laser patterning of ZnO crystals on the surface of borosilicate glass, *J. Am. Ceram. Soc.* 93 (2010) 658-661, <https://doi.org/10.1111/j.1551-2916.2009.03486.x>.
- 39 38. C. Bae and K.-S. Lim, Enhanced blue emission in  $\text{Er}^{3+}/\text{Yb}^{3+}$  doped glass-ceramics containing Ag nanoparticles and ZnO nanocrystals, *Curr. Opt. Photonics*, 3(2) (2019) 135–142, <https://doi.org/10.3807/COPP.2019.3.2.135>.
- 40 39. L.R. Pinckney, Transparent glass-ceramics based on ZnO crystals, *Phys. Chem. Glass. – Eur. J. Glass Sci. Technol. B* 47 (2006) 127–130, <https://www.ingentaconnect.com/content/sgt/ejgst/2006/00000047/00000002/art00010>.
- 41 40. W. Holand, G.H. Beall, *Glass-Ceramic Technology*, John Wiley & Sons, 2012.
- 42 41. Q. Luo, X. Qiao, X. Fan, X. Zhang, Near-infrared emission of  $\text{Yb}^{3+}$  through energy transfer from ZnO to  $\text{Yb}^{3+}$  in glass ceramic containing ZnO nanocrystals, *Opt. Lett.* 36 (2011) 2767-2769. <https://doi.org/10.1364/OL.36.002767>
- 43 42. B. Ghaemi, G. Zhao, G. Jie, H. Xi, X. Li, J. Wang, G. Han, A study of formation and photoluminescence properties of ZnO quantum dot doped zinc-alumino-silicate glass ceramic, *Optical Materials* 33 (2011) 827–830, doi:10.1016/j.optmat.2011.01.009.
- 44 43. B. Ghaemi, G. Zhao, S. Huang, J. Wang, G. Han, Structural and luminescence properties of Er-doped zinc–alumino–silicate glass ceramic, *J. Amer. Ceram. Soc.* 95 (2012) 1911–1914, <https://doi.org/10.1111/j.1551-2916.2012.05200.x>.
- 45 44. J. Zhou, S. Peng, H.J. Qin, B. Ghaemi, B. Song, G.L. Zhao, J.X. Wang, G.R. Han, Fabrication and visible emissions of ZnO nanocrystal doped transparent zinc silicate glass-ceramics, *J. Alloy. Compd.* 776 (2019) 52–58. <https://doi.org/10.1016/j.jallcom.2018.10.175>.

- 46 45. I.P. Alekseeva, O.S. Dymshits, A.A. Zhilin, S.S. Zapalova, D.V. Shemchuk, Transparent glass–ceramics based on ZnO and ZnO:Co<sup>2+</sup> nanocrystals, *J. Opt. Technol.* 81 (12) (2014) 723–728, <http://dx.doi.org/10.1364/JOT.81.000723>.
- 47 46. G.M. Arzumanyan, E.A. Kuznetsov, A.A. Zhilin, O.S. Dymshits, D.V. Shemchuk, I. P. Alekseeva, A.V. Mudryi, V.D. Zhivulko, O.M. Borodavchenko, Photoluminescence of transparent glass-ceramics based on ZnO nanocrystals and co-doped with Eu<sup>3+</sup>, Yb<sup>3+</sup> ions, *Opt. Mater.* 62 (2016) 666–672, <https://doi.org/10.1016/j.optmat.2016.10.054>.
- 48 47. P. Loiko, O. Dymshits, A. Volokitina, I. Alekseeva, D. Shemchuk, M. Tsenter, A. Bachina, A. Khubetsov, E. Vilejshikova, P. Petrov, A. Baranov, A. Zhilin, Structural transformations and optical properties of glass-ceramics based on ZnO, β- and α-Zn<sub>2</sub>SiO<sub>4</sub> nanocrystals and doped with Er<sub>2</sub>O<sub>3</sub> and Yb<sub>2</sub>O<sub>3</sub>: Part I. The role of heat-treatment, *J. Lumin.* 202 (2018) 47–56, <https://doi.org/10.1016/j.jlumin.2018.05.010>.
- 49 48. M. Shepilov, O. Dymshits, I. Alekseeva, A. Hubetsov, D. Shemchuk, A. Zhilin, Structure and anomalous light scattering of Er-doped transparent glass-ceramics containing ZnO nanocrystals, *J. Non-Cryst. Solids* 571 (2021) 121067(1-10), <https://doi.org/10.1016/j.jnoncrysol.2021.121067>.
- 50 49. Q. Yang, L. Zhao, H. Yu, Q. Min, C. Chen, D. Zhou, X. Yu, J. Qiu, B. Li., X. Xu, UV-shielding device of high-stability glass embedded with in-situ growth of ZnO quantum dots, *J. Alloys Compd.* 784 (2019) 535–540 <https://doi.org/10.1016/j.jallcom.2019.01.078>.
- 51 50. J. Zhou, B. Song, H. Qin, W. Lu, G. Zhao, Z. Huang, G. Han, Color-tunable and white emission of Tm<sup>3+</sup> doped transparent zinc silicate glass-ceramics embedding ZnO nanocrystals, *J Am Ceram Soc* 103 (2020) 1010–1017, <https://doi.org/10.1111/jace.16775>.
- 52 51. M. Duan, J. Wang, C. Liu, J. Xie, J. Han, Effects of SnO doping on the optical properties of ZnO in glass, *J. Non-Cryst. Solids* 459 (2017) 32–35, <https://doi.org/10.1016/J.JNONCRY SOL.2016.12.024>.
- 53 52. W. Lei, Z. Luo, Y. He, S. Liu, P. Zhang, H. Liang, A. Lu, Preparation and broadband white emission of Ce<sup>3+</sup>-doped transparent glass-ceramics containing ZnO nanocrystals for WLEDs applications, *J. Alloys Compd.* 875 (2021) 159979 (1-9), <https://doi.org/10.1016/j.jallcom.2021.159979>.
- 54 53. W. Lei, Z. Luo, Y. He, P. Zhang, S. Liu, A. Lu, ZrO<sub>2</sub>-doped transparent glass-ceramics embedding ZnO nano-crystalline with enhanced defect emission for potential yellow-light emitter applications, *Ceram. Intern.* 47 (2021) 35073–35080, <https://doi.org/10.1016/j.ceramint.2021.09.049>.

- 55 54. W. Lei, Z. Luo, H. Liang, Z. Zhou, C. Wen, Y. Wu, A. Lu, Enhanced defect emission of TiO<sub>2</sub>-doped transparent glass-ceramics embedding ZnO quantum dots with optimized heat-treatment schedule, *Ceram. Intern.*, <https://doi.org/10.1016/j.ceramint.2021.11.105>.
- 56 55. X. Du, H. Zhang, C. Cheng, S. Zhou, F. Zhang, Y. Yu, G. Dong, J. Qiu, Space-selective precipitation of ZnO crystals in glass by using high repetition rate femtosecond laser irradiation, *Opt. Express*, 22 (2014) 17908(1-7), <https://doi.org/10.1364/OE.22.017908>.
- 57 56. C. Lin, J. Wang, X. Zhao, E. Zhu, N. Long, C. Rüssel, Competitive crystallization of  $\beta$ -Zn<sub>2</sub>SiO<sub>4</sub> and ZnO in an aluminosilicate glass, *Ceram. Int.* 44 (2018) 7209–7213, <https://doi.org/10.1016/j.ceramint.2018.01.168>.
- 58 57. MAUD materials analysis using diffraction, a Rietveld extended program to perform the combined analysis, <http://maud.radiographema.eu/>.
- 59 58. L. Lutterotti, R. Ceccato, R. Dal Maschio, E. Pagani, Quantitative analysis of silicate glass in ceramic materials by the Rietveld method, *Mater. Sci. Forum* 278-281 (1998) 87–92, <https://doi.org/10.4028/www.scientific.net/MSF.278-281.87>
- 60 59. H. Lipson, H. Steeple, Interpretation of X-ray powder diffraction patterns, Macmillan, London, 1970.39.
- 61 60. J.A.R. Márquez, C.M.B. Rodríguez, C.M. Herrera, E.R. Rosas, O.Z. Angel, O.T. Pozos, Effect of surface morphology of ZnO electrodeposited on photocatalytic oxidation of methylene blue dye. Part I: Analytical study, *Int. J. Electrochem. Sci.* 6 (2011) 4059–4069.
- 62 61. V.N. Filipovich, Toward the theory of Small-Angle X-ray Scattering, *Zh. Tekh. Fiz.* 26(2) (1956) 398—416.
- 63 62. N.S. Andreev, V.N. Filipovich, O.V. Mazurin, E.A. Porai-Koshits, G.P. Roskova, Phase Separation in Glass, Elsevier Science Publishers B.V, Amsterdam, North-Holland, 1984<http://store.elsevier.com/Phase-Separation-in-Glass/isbn-9780080983653/>.
- 64 63. M.P. Shepilov, O.S. Dymshits, A.A. Zhilin, S.S. Zapalova, On the measurements of scattering coefficient of nanostructured glass-ceramics by a serial spectrophotometer, *Measurement* 95 (2017) 306-316. <http://dx.doi.org/10.1016/j.measurement.2016.10.014>.
- 65 64 63. I. Alekseeva, O. Dymshits, M. Tsenter, A. Zhilin, V. Golubkov, I. Denisov, N. Skoptsov, A. Malyarevich, K. Yumashev, Optical applications of glass-ceramics, *J. Non-Cryst. Solids* 356 (52–54) (2010) 3042–3058, <http://dx.doi.org/10.1016/j.jnoncrysol.2010.05.103>.
66. P. Loiko, O. Dymshits, A. Volokitina, I. Alekseeva, D. Shemchuk, M. Tsenter, A. Bachina, A. Khubetsov, E. Vilejshikova, P. Petrov, A. Baranov, A. Zhilin, Structural transformations and optical properties of glass-ceramics based on ZnO,  $\beta$ - and  $\alpha$ -Zn<sub>2</sub>SiO<sub>4</sub> nanocrystals and doped with Er<sub>2</sub>O<sub>3</sub> and Yb<sub>2</sub>O<sub>3</sub>: Part I. The role of heat-treatment, *J. Lumin.* 202 (2018) 47–56, <https://doi.org/10.1016/j.jlumin.2018.05.010>



67 66 65 64. P. MacMillan, B. Piriou, A. Navrotsky, A Raman spectroscopic study of glasses along the joins silica-calcium aluminate, silica-sodium aluminate, and silica-potassium aluminate, *Geochim. Cosmochim. Acta*, 46 (11) (1982) 2021-2037, [https://doi.org/10.1016/0016-7037\(82\)90182-X](https://doi.org/10.1016/0016-7037(82)90182-X).

68 67 66 65. F.A. Seifert, B.O. Mysen, D. Virgo, Three dimensional network melt structure in the systems  $\text{SiO}_2\text{-NaAlO}_2$ ,  $\text{SiO}_2\text{-CaAl}_2\text{O}_4$  and  $\text{SiO}_2\text{-MgAl}_2\text{O}_4$ , *Amer. Miner.* 67 (7,8) (1982) 696-718.

69 68 67 66. D.W. Matson, S.K. Sarma, J.A. Philpotts, Raman spectra of some tecto silicates and of glasses along the orthoclase-anorthite and nepheline-anorthite joins, *Am. Mineral.* 71 (1986) 694-704.

70 69 68 67. C.A. Arguello, D.L. Rousseau, S.P.S. Porto, First-order Raman effect in wurtzite-type crystals, *Phys. Rev.* 181 (1969) 1351-1363, <https://doi.org/10.1103/PhysRev.181.1351>.

71 70 69 68. P.A. Loiko, O.S. Dymshits, V.V. Vitkin, N.A. Skoptsov, A.A. Zhilin, D.V. Shemchuk, M.Ya. Tsenter, K.V. Bogdanov, A.M. Malyarevich, I.V. Glazunov, X. Mateos, K.V. Yumashev, Structure and nonlinear optical properties of novel transparent glass-ceramics based on  $\text{Co}^{2+}\text{:ZnO}$  nanocrystals, *Laser Phys. Lett.* 13 (2016) 055803 (7pp), <https://doi.org/10.1088/1612-2011/13/5/055803>.

72 71 70 69. P.A. Loiko, O.S. Dymshits, V.V. Vitkin, N.A. Skoptsov, A.A. Zhilin, D.V. Shemchuk, M.Ya. Tsenter, K.V. Bogdanov, A.M. Malyarevich, I.V. Glazunov, X. Mateos, K.V. Yumashev, Saturable absorber: transparent glass-ceramics based on a mixture of  $\text{Co}:\beta\text{-Zn}_2\text{SiO}_4$  and  $\text{Co}:\text{ZnO}$  nanocrystals, *Appl. Opt.* 55 (21) (2016) 5505-5512, <http://dx.doi.org/10.1364/AO.55.005505>.

73 72 71 70. N.N. Ovsyuk, S.V. Gorya, Amorphous-to-amorphous phase transition in zeolites, *JETP Lett.* 83 (2006) 109-112, <https://doi.org/10.1134/S0021364006030064>.

74. R. Pappalardo, D.L. Wood, R.C. Linares, Jr., Optical absorption study of co-doped oxide systems. II, *J. Chem. Phys.* 35 (1961) 2041–2060, <https://doi.org/10.1063/1.1732208>.

75. Y.Z. Peng, T. Liew, W.D. Song, C.W. An, K.L. Teo, T.C. Chong, *J. Supercond.* 18 (2005) 97-103, <https://doi.org/10.1007/s10948-005-2158-4>.

76. S. Guo, X. Zhang, Y. Huang, Y. Li, Z. Du, Investigation on electronic structures and nature of charge-transfer transition of  $\text{ZnO}:\text{Co}$  with variation of Co content, *Chem. Phys. Lett.* 459 (2008) 82-84, <https://doi.org/10.1016/j.cplett.2008.03.071>.

77. L. Galois, G. Calas, Structural environment of nickel in silicate glass/melt systems: Part 1. Spectroscopic determination of coordination states, *Geochim. Cosmochim. Acta* 57 (1993) 3613-3626, [https://doi.org/10.1016/0016-7037\(93\)90143-K](https://doi.org/10.1016/0016-7037(93)90143-K).

78. R. Pappalardo, D.L. Wood, R.C. Linares, Optical absorption spectra of Ni doped oxide systems. I, *J. Chem. Phys.* 35(4) (1961) 1460–1480, <http://dx.doi.org/10.1063/1.1732066>.



79. G.T. Chandrappa, S. Ghosh, K.C. Patil, Synthesis and properties of willemite,  $Zn_2SiO_4$ , and  $M^{2+}:Zn_2SiO_4$  (M = Co and Ni), *J. Mater. Syn. Proc.* 7(5) (1999) 273-279,
80. M. Shepilov, O. Dymshits, I. Alekseeva, A. Hubetsov, D. Shemchuk, A. Zhilin, Structure and anomalous light scattering of Er-doped transparent glass-ceramics containing ZnO nanocrystals, *J. Non-Cryst. Solids* 571 (2021) 121067(1-10), <https://doi.org/10.1016/j.jnoncrysol.2021.121067>.
81. O.S. Dymshits, A.A. Zhilin, T.I. Chuvaeva, M.P. Shepilov, Structural states of Ni(II) in glasses and glass-ceramic materials of the lithium-aluminium-silicate system *J. Non-Cryst. Solids* 127 (1991) 44-52, [https://doi.org/10.1016/0022-3093\(91\)90399-Q](https://doi.org/10.1016/0022-3093(91)90399-Q).
82. D.L. Russell, K. Holliday, M. Grinberg, D.B. Hollis, Broadening of optical transitions in  $Cr^{3+}$ -doped aluminosilicate glasses, *Phys. Rev. B* 59(21) 13712-13718, <https://doi.org/10.1103/PhysRevB.59.13712>.
83. K. Tanaka, I. Yamaguchi, K. Hirao, N. Soga, Optical properties of transparent glass-ceramics containing  $ZnGa_2O_4 : Cr^{3+}$  microcrystals, *Bull. Inst. Chem. Res., Kyoto Univ.*, 72(2) (1994) 124-133.
84. B. Babu, V.P. Manjari, T. Aswani, G.T. Rao, R.J. Stella, R.V.S.S.N. Ravikumar, Structural, optical and magnetic properties of  $Cr^{3+}$  doped ZnO nanopowder, *Indian J. Phys.* 88(7) (2014) 683-690, <https://doi.org/10.1007/s12648-014-0473-y>.
85. B.C. Babu, G.-G. Wang, B. Yan, Q. Yang, A.P. Baker, Effects of  $Cr^{3+}$  addition on the structure and optical properties of  $\alpha$ - $Zn_2SiO_4$  synthesized by sol-gel method, *Ceram. Int.* 44(1) (2018) 938-946, <https://doi.org/10.1016/j.ceramint.2017.10.026>.
86. W. Streck, P. Deren, B. Jezowska-Trzebiatowska, Optical properties of  $Cr^{3+}$  in  $MgAl_2O_4$  spinel, *Physica B*, 152 (1988) 379-384.
87. W. Nie, F.M. Michel-Calandini, C. Linares, G. Boulon, C. Daul, New results on optical properties and term-energy calculations in  $Cr^{3+}$ -doped  $ZnAl_2O_4$ , *J. Lumin.*, 46(3) (1990) 177-190, [https://doi.org/10.1016/0022-2313\(90\)90038-D](https://doi.org/10.1016/0022-2313(90)90038-D).
- 88.78. E. Gorokhova, I. Venetsev, I. Alekseeva, A. Khubetsov, O. Dymshits, L. Basyrova, E. Oreschenko, S. Eron'ko, F. Muktepavela, K. Kundzins, A. Zhilin, P. Loiko, Effect of  $Yb^{3+}$  doping level on the structure and spectroscopic properties of ZnO optical ceramics, *J. Phys.: Conf. Ser.* 2086 (2021) 012015(1-6), <https://doi.org/10.1088/1742-6596/2086/1/012015>.
8979. E. Gorokhova, O. Dymshits, I. Venetsev, L. Basyrova, I. Alekseeva, A. Khubetsov, M. Baranov, M. Tsenter, A. Zhilin, S. Eron'ko, E. Oreschenko, F. Muktepavela, K. Kundzins, P. Loiko, ZnO –  $Yb_2O_3$  composite optical ceramics: Synthesis, structure and spectral-luminescent properties, *J. Eur. Ceram. Soc.*, 42 (2) (2022) 616-630, <https://doi.org/10.1016/j.jeurceramsoc.2021.10.031>.

9080. M.J. Sienko, R.A. Plane, R.E. Hester, Inorganic chemistry. Principles and elements, Cornell University, 1965, New York, Amsterdam, 188 p.
9181. D. Barreca, C. Massignan, S. Daolio, M. Fabrizio, C. Piccirillo, L. Armelao, E.o Tondello, Composition and microstructure of cobalt oxide thin films obtained from a novel cobalt(II) precursor by chemical vapor deposition, *Chem. Mater.* 13(2) (2001) 588–593.
9282. P. Loiko, A. Belyaev, O. Dymshits, I. Evdokimov, V. Vitkin, K. Volkova, M. Tsenter, A. Volokitina, M. Baranov, E. Vilejshikova, A. Baranov, A Zhilin, Synthesis, characterization and absorption saturation of Co:ZnAl<sub>2</sub>O<sub>4</sub> (gahnite) transparent ceramic and glass-ceramics: a comparative study, *J. Alloys Compd.* 725 (2017) 998–1005, <https://doi.org/10.1016/j.jallcom.2017.07.239>.
9383. L. Basyrova, V. Bukina, S. Balabanov, A. Belyaev, V. Drobotenko, O. Dymshits, I. Alekseeva, M. Tsenter, S. Zapalova, A. Khubetsov, A. Zhilin, A. Volokitina, V. Vitkin, X. Mateos, J.M. Serres, P. Camy, P. Loiko, Synthesis, structure and spectroscopy of Fe<sup>2+</sup>:MgAl<sub>2</sub>O<sub>4</sub> transparent ceramics and glass-ceramics, *J. Lumin.* 236 (2021) 118090 (1-17), <https://doi.org/10.1016/j.jlumin.2021.118090>.
94. R. Cusco, E. Alarcon-Llado, J. Ibanez, L. Artus, J. Jimenez, B. Wang, M. J. Callahan, Temperature dependence of Raman scattering in ZnO, *Phys. Rev. B* 75 (2007) 165202-1-11, <https://doi.org/10.1103/PhysRevB.75.165202>.