



## Theory and molecular simulations of plasma sputtering, transport and deposition processes

Pascal Brault, Anne-Lise Thomann, Marjorie Cavarroc

### ► To cite this version:

Pascal Brault, Anne-Lise Thomann, Marjorie Cavarroc. Theory and molecular simulations of plasma sputtering, transport and deposition processes. *The European Physical Journal D : Atomic, molecular, optical and plasma physics*, 2023, 77 (2), pp.19. 10.1140/epjd/s10053-023-00592-x . hal-03921537

HAL Id: hal-03921537

<https://hal.science/hal-03921537>

Submitted on 3 Jan 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

## Theory and molecular simulations of plasma sputtering, transport and deposition processes

Pascal Brault<sup>1\*</sup>, Anne-Lise Thomann<sup>1</sup>, Marjorie Cavarroc<sup>2</sup>

<sup>1</sup>GREMI CNRS – Université d’Orléans, 14 rue d’Issoudun, BP6744, 45067 Orléans Cedex 2, France

<sup>2</sup>SAFRAN Tech, Rue des jeunes bois, Chateaufort, CS 80112, 78772 Magny-les-Hameaux, France

\*Corresponding author: [pascal.brault@univ-orleans.fr](mailto:pascal.brault@univ-orleans.fr)


**ORCID** Pascal Brault 0000-0002-8380-480X

**Abstract:** The present review provides an overview of the basic theory of sputtering with recent models, focussing in particular on sputtered atom energy distribution functions. Molecular models such as Monte-Carlo, kinetic Monte-Carlo, and classical Molecular Dynamics simulations are presented due to their ability to describe the various processes involved in sputter deposition at the atomic and molecular scale as required. The sputter plasma, the sputtering mechanisms, the transport of sputtered material and its deposition leading to thin film growth can be addressed using these molecular simulations. In all cases, the underlying methodologies and some selected mechanisms are highlighted.

## 1. Introduction

Plasma sputtering is a widely used deposition method that belongs to physical vapor deposition (PVD) techniques. Its basic principle is the sputtering of a negatively biased target (called the cathode) by ions present in a (reactive) plasma. The plasma is ignited by the electrical breakdown when applying a high voltage between the cathode/target and the grounded part of the vessel or by an external antenna as in Inductively Coupled Plasma (ICP) sources. In these cases ions are created in the plasma chamber. Those close to the target will be accelerated by the cathode potential fall. If they acquire enough energy, i.e., above a threshold (depending on the nature of the cathode/target), the impinging ions will sputter the target. The plasma source defines the operating regime: magnetron sputtering, cathodic sputtering using either a closed coupled plasma or an externally coupled plasma with a high frequency antenna. In all cases, the sputtering/deposition process comprises the following steps: ion creation, impingement of the ions on the biased target, sputtering of the target material and transport of the sputtered atoms toward the substrate.


During the flight to substrate, sputtered atoms can react with the plasma reactive species to form molecules, or if the pressure is high enough, atom condensation can occur, and cluster formation becomes possible in the plasma phase. The principle of plasma sputtering is summarized in Figure 1.

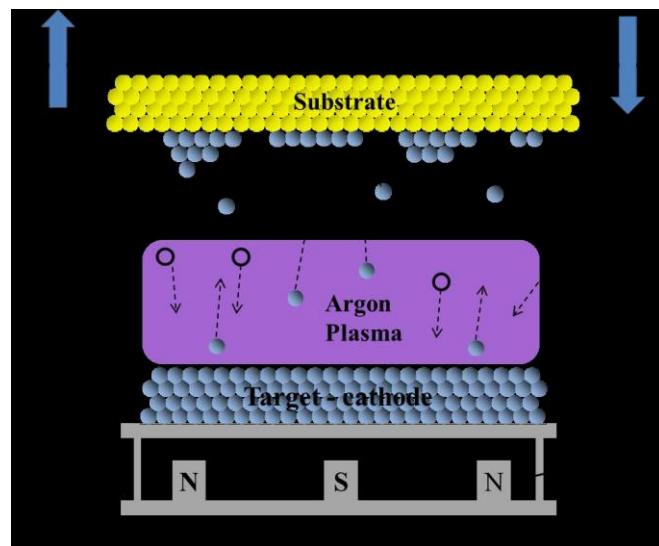

**Figure 1.** A simple schematic of plasma sputtering. Reprinted from Ref. [1]

There are several types of plasma sputtering. The most popular one is magnetron sputtering in which permanent magnetic fields are placed below the cathode so that the electrons are trapped, which has the effect of confining the ionization close to the cathode [2]. In turn, this increases the sputtering rate and the cathode current, while the positive ions created impinge the target with an energy corresponding to the cathode negative bias  $V_b$ , with the maximum value of  $eV_b$ . Variants

using different types of magnet result in different sizes of plasma in front of the substrate, as summarized in figure 2.

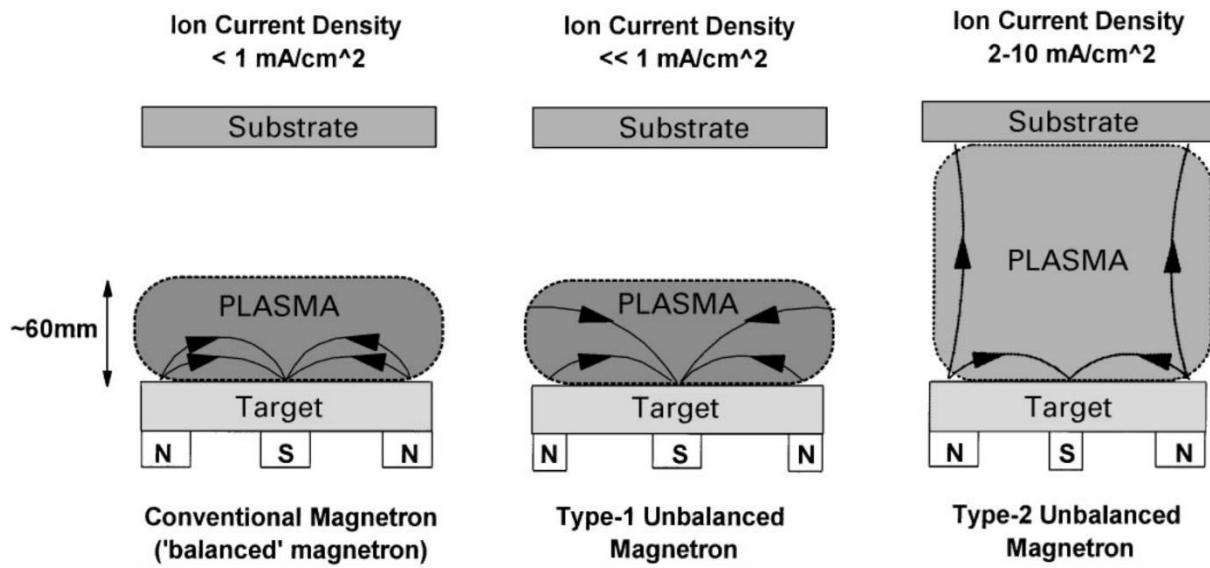


**Figure 2.** Different types of magnetron configurations. Reprinted from Ref. [2]

The cathode can be powered by continuous or pulsed direct current (DC), alternative current (AC), or radiofrequency (RF) sources. An improvement is to use a pulsed DC source with a high-power very short pulse duration, the so-called HiPIMS (High Power impulse Magnetron Sputtering) or HPPMS (high-power pulsed magnetron sputtering) [3]. For all these configurations, the sputtering gas can be either neutral (e.g., Argon, Helium) or reactive (e.g., Oxygen, nitrogen, ammonia, methane, often mixed with a non-reactive gas such as Argon, Helium, etc.) [4]. DC sputtering requires that the target remain conductive during the entire process.

Studying the sputtering process requires finding what is common to all these configurations. However, it is also important to focus on different specific issues in order to understand how plasma features are affected. The basic information sought is the nature of the sputtered species, the sputtering yields, i.e., the ratio of sputtered atoms per incident ions, and the energy distribution functions. The present study will describe how analytical modeling and computer simulations deal with calculating and/or predicting these parameters, but will also describe the generated plasma itself.

The general scheme of simulations, highlighting the necessary steps to be accomplished to fully describe magnetron plasma sputter deposition, called “virtual sputter magnetron” [5] is summarized in Figure 3.

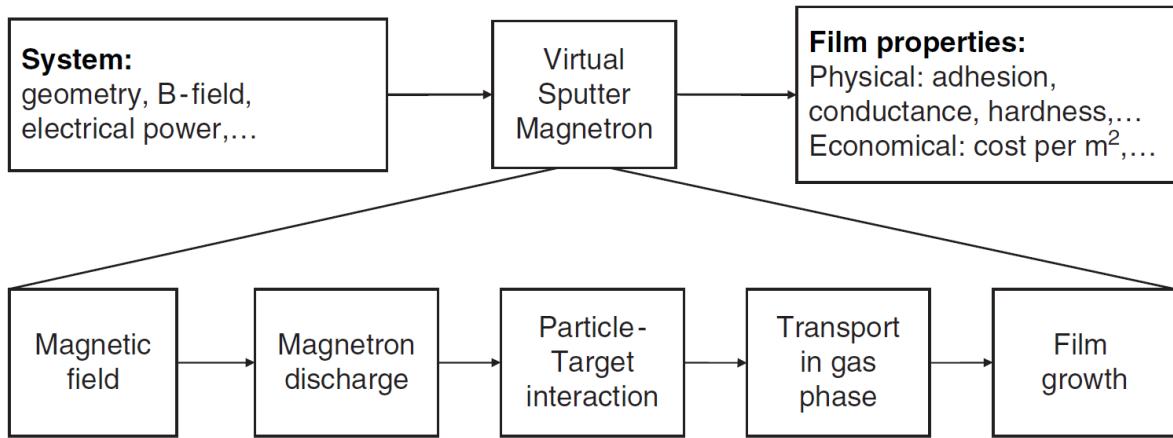


**Figure 3.** General scheme of the simulation parts needed to build a “virtual sputter magnetron”.  
reprinted from Ref. 5

This review will be organized along the three main components, plasma and sputtering -transport-deposition/growth, for plasmas with a bias below 1kV. Ion sputtering/implantation in the keV region and above are beyond the scope of this review. While section 2 is devoted to sputtering theory, the third section presents Monte-Carlo approaches to magnetron discharge modelling. The fourth section is devoted to the different numerical simulations of plasma sputtering, transport and deposition using atomistic models: Monte-Carlo, kinetic Monte-Carlo, and Molecular Dynamics.

## 2. Sputtering models

This part reviews the basic concepts of sputtering from the point of view of target sputtering as well as the properties of the sputtered material.

The theory of sputtering aims at describing the physics of the interaction of an incoming ion with atoms of a material. Depending on the colliding atom or the ion kinetic energy, successive phenomena occur at the surface and in the depth of the target, which results in the ejection of an atom as described in Figure 4 [6].

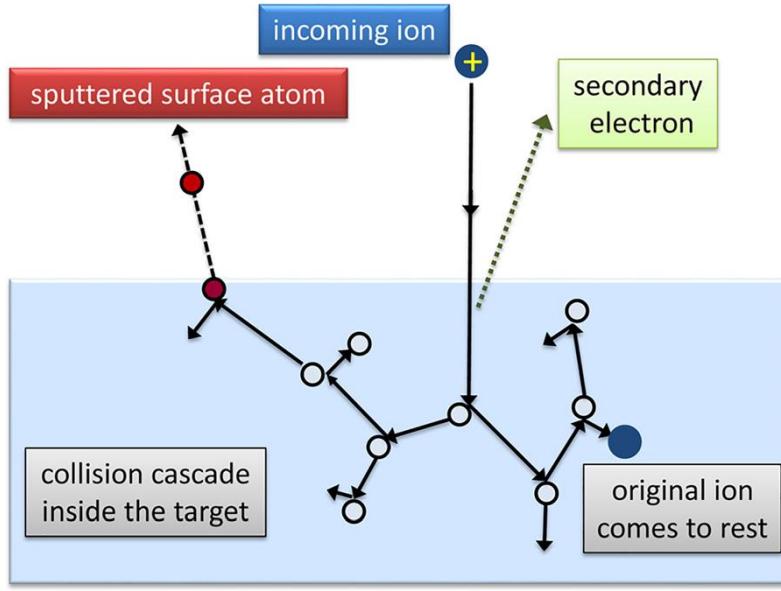

**Figure 4.** Schematic describing the main steps of a sputtering event resulting from the interaction of an incoming ion with target atoms up to surface atom ejection and the original ion coming to rest in the target (Reprinted from Ref. 6).

Sputtering theory provides an analytical formula to obtain the sputtering rate  $\gamma_{sputt}$ , i.e. the ratio of the number of sputtered target atoms  $N_t$  to the number of incident ions  $N_i$ , i.e.  $Y = \frac{N_t}{N_i}$ , and the energy distribution function of the sputtered atoms. For complex systems such as molecular solids (metal oxides, organics, etc.), more than one species or molecules and small clusters can be ejected, making it almost impossible to deduce a practical analytical formula. In these cases, it will be more appropriate to use atomistic modelling (see section 5 below).

Many publications have addressed the foundation of sputtering mechanism theories [2,4–43]. The pioneering theory proposed by Townes in 1944 [7] provided the first analytical expression of sputtering yield in a glow discharge, depending on cathode fall and discharge current, since the initial experimental work reported in 1852 [44] by Grove. Reasonable agreement with experiment was found at low bias voltage and high pressure. The next most referenced contribution came from Sigmund's work [15, 16, 22, 24, 32] dedicated to both sputtering yields and the kinetic energy distribution of sputtered species of pure and multicomponent targets.

A frequently used analytical sputtering yield  $\gamma_{sputt}$  [45, 46] is provided in the form:

$$Y(E) = 0.042 \frac{Q(Z_2)\alpha^*(m_g/m_s)}{U_s} \frac{S_n(E)}{1 + \Gamma k \varepsilon^{0.3}} \left[ 1 - \sqrt{\frac{E_{th}}{E}} \right]^s \quad (1)$$

where  $E$  is the incoming sputtering ion energy,  $m_i$  and  $m_t$  are the masses of ion and target atom in atomic mass units respectively, and the numerical factor in units of  $\text{\AA}^{-2}$ .  $U_s$  is the target surface binding energy,  $E_{th}$  is the sputtering threshold energy,  $S_n(E)$  is the stopping power, and  $\Gamma$ ,  $Q$  and  $\alpha^*$  are (fitting) parameters [45]. It is based on the Sigmund theory [15] using the Ziegler-Biersack-Littmark (ZBL) [47] screened repulsive potential and including the Lindhard electronic stopping power [48]. As sputtering can only occur if the surface is able to break its bond with neighboring surface atoms, the incoming ions should exceed a threshold energy  $E_{th}$ . This energy threshold is a function of the surface atom binding energy  $E_s$  [45]:


$$E_{th} = E_s \begin{cases} 1 + 1.57 \frac{m_i}{\gamma \cdot m_t}; & m_i < m_t \\ \frac{6.7}{\gamma}; & m_i \geq m_t \end{cases} \quad (2)$$

and with  $\gamma = 4 \frac{m_i m_t}{(m_i + m_t)^2}$  being the energy transfer in a direct collision. All the parameters needed for evaluating  $Y(E)$  are available in Refs. [6, 45].

On the other hand, the sputtering yield scales with ion energy as [5].

$$Y(E) = aE^b \quad (3)$$

$a$  and  $b$  being adjustable parameters that depend on the nature of the incoming ion (for kinetic energy less than 3keV) and the target material [6]. Fitted values of  $a$  and  $b$  are available in Ref. 6. For illustration, Figure 5 displays the sputtering yields of silicon by  $\text{Ar}^+$  and  $\text{He}^+$  ions in the range 0 - 1000 eV, calculated from equation (1). The effect of the mass ratio  $\gamma$  is clearly visible: a large difference in the masses of impinging ions and a defined target element results in a lower sputtering yield.

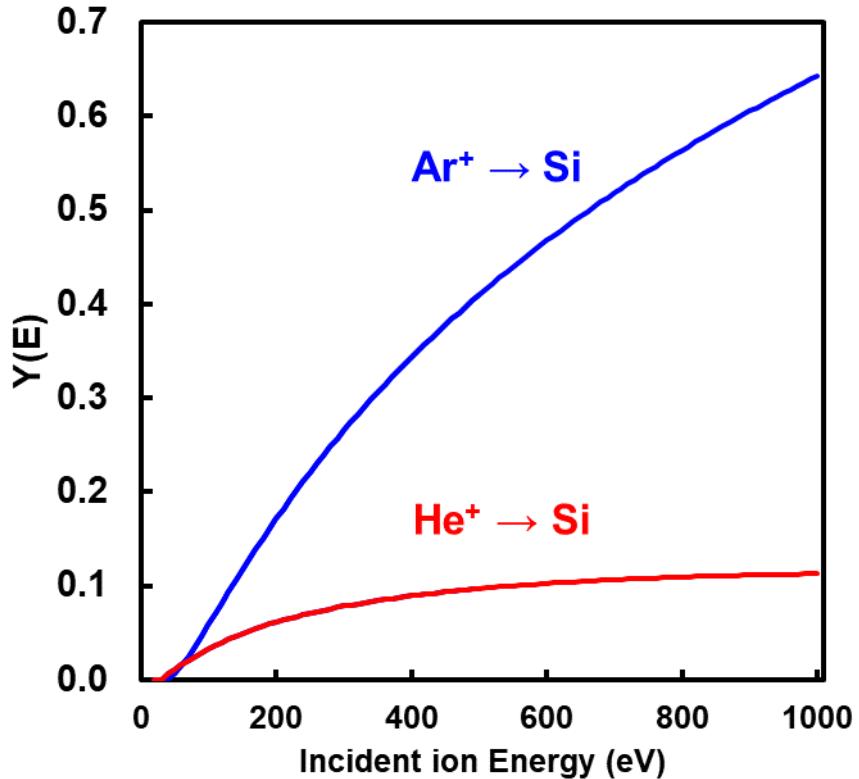

**Figure 5.** Plot of the sputtering yields of Si by  $\text{Ar}^+$  and  $\text{He}^+$  ions with kinetic energies up to 1000 eV calculated from Equation (1)

A second important parameter is the sputtered atom energy distribution function, since it describes the energy that will be deposited during deposition after travelling the path from target to substrate. During flight, the sputtered atoms will lose energy by collision with the background plasma-forming gas. This will impact the energy distribution function at the substrate.


A very popular sputtered atom energy distribution function (EDF)  $F(E)$  was developed by Thompson [19], which reads:

$$F(E) = \begin{cases} \propto \frac{1 - \left(\frac{E_s + E}{\gamma E_i}\right)^{\frac{1}{2}}}{E^2 \left(1 + \frac{E_s}{E}\right)^3}, & E < \gamma E_i - E_s \\ 0, & E > \gamma E_i - E_s \end{cases} \quad (4)$$

where  $E_s$  is the binding energy of the target surface atoms, and  $E$  is the energy of the sputtered atoms.

This EDF behaves as  $E^{-2}$  for a large sputtered atom energy  $E$ , showing that the contribution of the distribution tail can be significant. The maximum of the distribution is located at  $E_s/2$  and the width

is on the order of a few eV (5 to 20 eV) when the incoming ion is Ar. Figure 6 displays the example of Si sputtered by Ar and He. Contrary to the sputtering yield, the different mass ratios do not significantly affect the sputtered atom EDF.

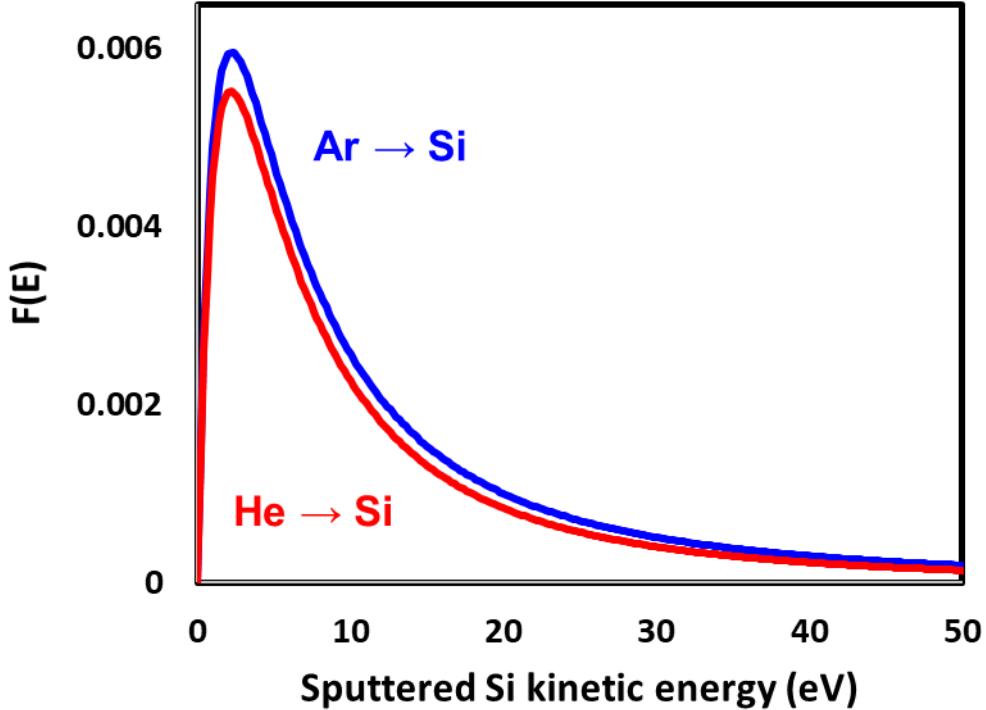

**Figure 6.** The Thompson Energy Distribution function (Equation 4) of sputtered Si by Ar and He ions calculated at the same kinetic energy of 400 eV.


An analytical improvement in the sputtered atom EDF was recently achieved and is known as the Stepanova EDF [39, 40], which reads:

$$F(E) = \frac{E}{(E + E_s)^3} \exp \left[ -A \left( \frac{m_i(E \cos^{q_1} \theta + E_s)}{m_t E_i} \right)^{q_2} \right] \times \left( 1 - \frac{E + E_s}{E_{max} + E_s} \right) \quad (5)$$

where  $E_{max}$  is a cutoff factor allowing  $F(E)$  to vanish for  $E > E_{max}$  with  $E_{max} = \frac{E_s}{E_{th}} E_i$ ,  $q_1 \approx 2 - \frac{m_t}{4m_i}$ ,  $q_2 = 0.55$  and  $A = 13$  [39].

It accounts for anisotropy effects at low incident ion energy which results in narrowing of the EDF in agreement with Monte-Carlo simulations [49, 50]. This effect is not included in the Thompson

distribution. To illustrate how Stepanova EDF behaves, Figure 7 displays a typical comparison with experiments, modeling, and Thompson distribution.

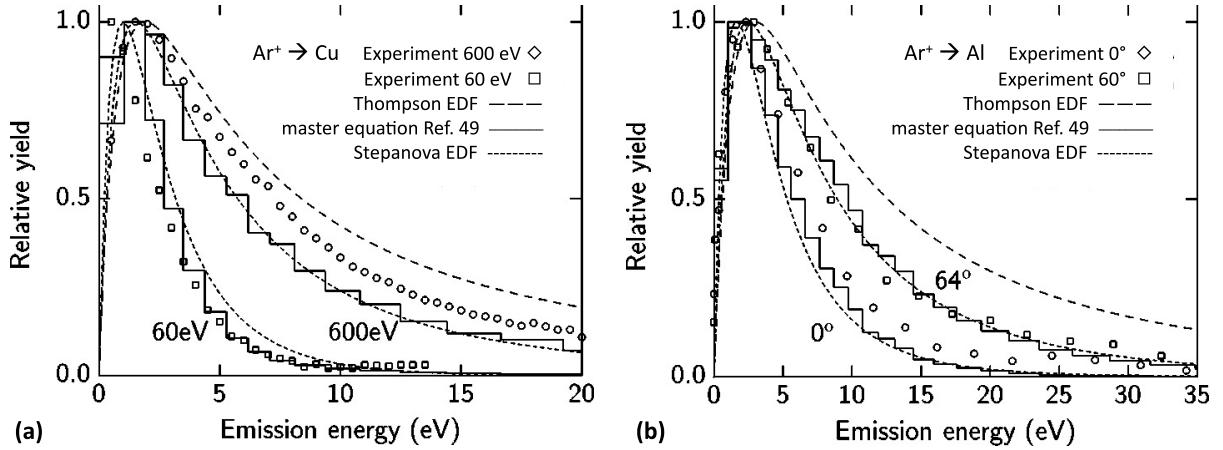

**Figure 7.** Plots of the Stepanova energy distribution function compared to the Thompson distribution, master equation (stepped lines) and experiments at different ion incident energies for  $\text{Ar}^+$  on Cu (a) and angles for  $\text{Ar}^+$  on Al (b). Adapted from Figures 10 and 11 of Ref. 39.

Other deviations from the Thompson formula have been observed in the case of light incident ions impacting heavy target atoms. Assuming that sputtered atoms are only primary recoil atoms, the following Falcone formula was derived [32]


$$F(E) = \frac{E}{(E + E_s)^{5/2}} \ln \frac{\gamma E_i}{E + E_s} \quad (5)$$

A further slight improvement, also for light ion sputtering, was carried out by Kenmotsu [46, 54], leading to:

$$F(E) = \frac{E}{(E + E_s)^{8/5}} \left[ \ln \frac{\gamma(1 - \gamma)E_i}{E + E_s} \right]^2 \quad (6)$$

Note that contrary to the Thompson formula (4), the Falcone and Kenmotsu EDF formulae depend on the incoming energy  $E_i$ . Moreover, anisotropic effects at low energy are not considered, as in Thompson distribution.

Figure 8 displays a comparison between EDFs described by the various EDF formulae for light and heavier ions at 2 different energies. Since the Kenmotsu formula is optimized for light ions, it fails to produce a reasonable EDF for  $\text{Ar}^+$  ion sputtering at low energy, as shown in Fig. 8. (a). The incident energy dependence of the Stepanova, Kenmotsu and to a lesser extent Falcone formulae is well observed. For Falcone the dependence is more visible for light ion  $\text{He}^+$ , since the Falcone formula holds for light ions.

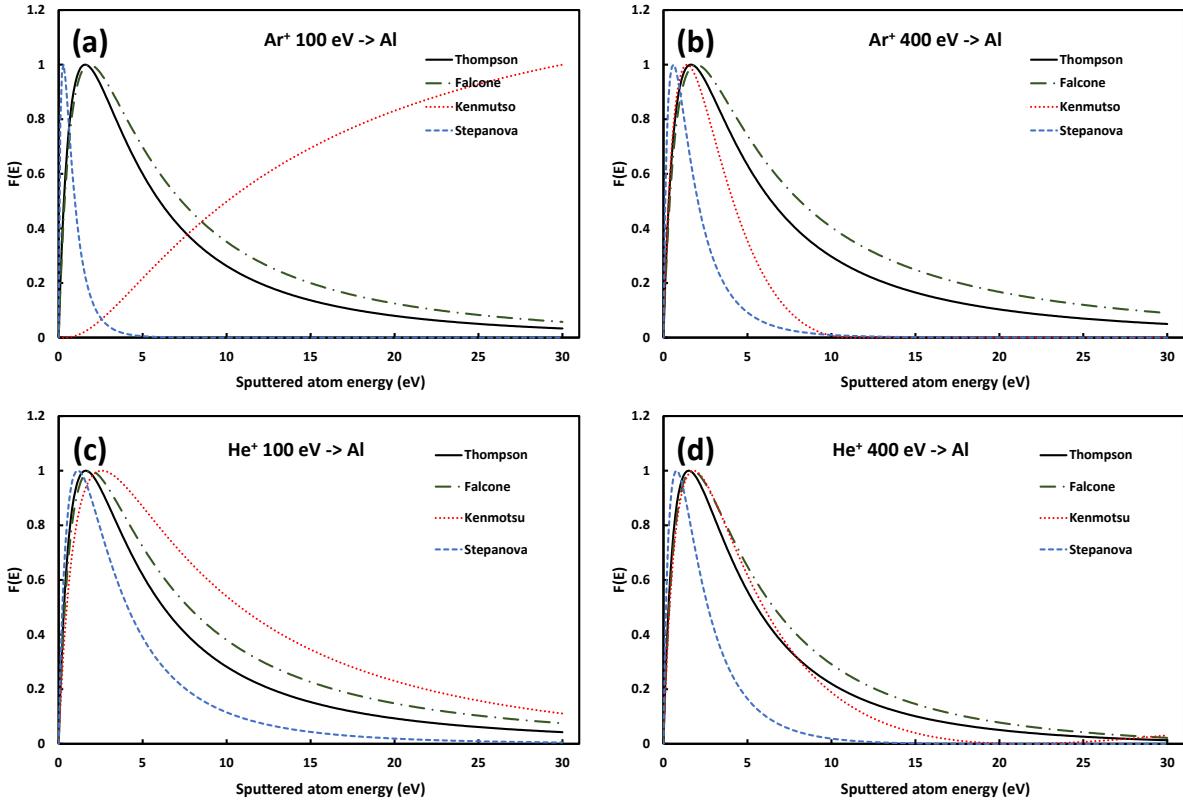


**Figure 8:** Plots of Thompson, Falcone, Kenmotsu and Stepanova Energy distribution functions for (a, b) incident Ar<sup>+</sup> and (c, d) incident He<sup>+</sup> ions, both with kinetic energy of 100 and 400 eV

After the sputtering occurs, the sputtered materials as well as the reflected incident ions travel across the plasma which is mainly composed of neutral species since the ionized species fraction in DC, RF or pulsed DC magnetron sputtering ranges from  $10^{-5}$  to  $10^{-3}$ . This can reach a value close to 1 in an HiPIMS configuration. Sputtered atoms travelling across the region between target and substrate, will suffer collisions with the ambient gas and lose part of their kinetic energy modifying their EDF. An elegant analytical approach has been developed which considers, in a first approximation, the energy losses along a pathway normal to the substrate, i.e., without accounting for angular effects [51, 52]. The mean kinetic energy is thus, at distance  $d$  from the target, is thus given by:

$$E_F = (E - k_B T_g) \exp \left[ n \cdot \ln \left( \frac{E_f}{E_i} \right) \right] + k_B T_g \quad (7)$$

$E_F$  being the kinetic energy after  $n$  collisions.  $\frac{E_f}{E_i} = 1 - \gamma/2$  is the kinetic energy ratio after and before a collision.  $n = dP\tau/k_B T_g$  is the number of collisions along the path,  $P$  and  $T_g$  are the sputtering gas pressure and temperature, and  $\tau$  is the collision cross section assuming, for example, hard core interactions. The energy loss ( $E_f$ ) of the sputtered atoms with the gas atoms is calculated considering

a Maxwell–Boltzmann (MB) distribution at  $E_g = k_B T_g$ . For each  $E_g$  in the MB gas distribution, the energy loss is calculated for a fixed value of the kinetic energy  $E$  of a sputtered atom. This is repeated for each  $E$  of any EDF  $F(E)$ , and weighted by the collision probability, which is simply the convolution of  $F(E)$  and the MB distribution at  $T_g$  [51]. It should be mentioned that the key parameter in equation (5) is the product  $P.d$  that drives the collision number  $n$ : varying  $P$  or  $d$  keeping  $P.d$  constant thus results in the same  $f(E)$  at distance  $d$  from the target. Figure 9 shows how the EDF evolves against pressure  $P$ . At sufficiently high  $P$  or  $d$  values, the sputtered atom EDF becomes a Maxwell-Boltzmann distribution.

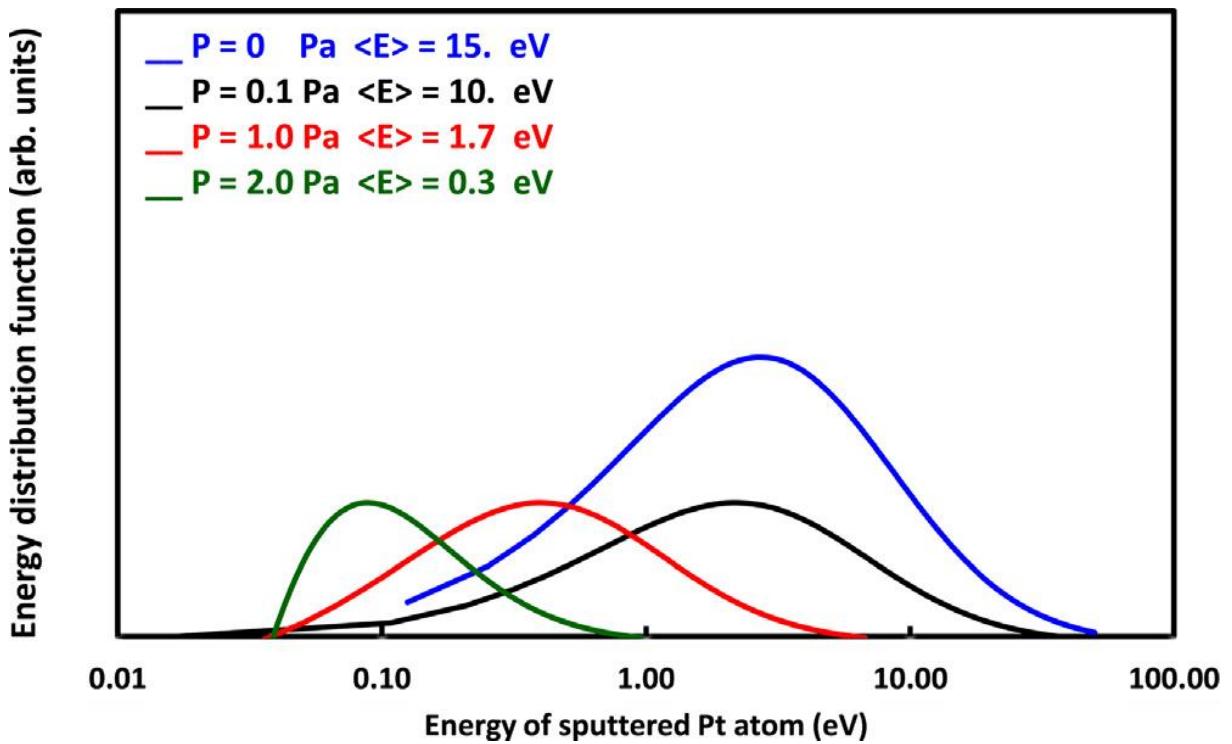

**Figure 9:** Example of sputtered Pt atom EDF for a fixed target to substrate distance  $d = 10$  cm and varying pressure. The target potential is fixed at 300V. For clarity, a log scale is used for the horizontal energy scale. Mean kinetic energies of the resulting EDFs are reported for each pressure. Reprinted from Ref. 53.

For the specific case of HiPIMS, this procedure can be used provided that the EDF accounting for both neutral and ions is properly included.

Reactive Magnetron sputtering is a more complex situation since the ambient (sputtering) gas, often a mixture of a reactive gas such as  $O_2$ ,  $NH_3$ ,  $CH_4$ , etc., can react with the target subjected to the incident ions. In unreactive sputtering by inert gases, it is expected that ions implanted in the target will not modify the sputtering, mainly because these ions do not react and do not modify the

properties of the physical target, except for local distortions of the lattice. Even if this assumption is questionable, it underlies almost all sputtering models. When reactive species interact with the target, both chemical composition and physical properties (conducting/semi-conducting and insulating state) are changed. Change in the target chemical composition due to reactive species is often called the target poisoning effect. Moreover, it depends on which reactive flux, the (initially conducting) target is exposed to. And thus, the sputtering can be severely affected. A simple analytical model known as Berg's model [55-63] has been devised and provides sputtering rates (as well as deposition rates). It is based on the balance between the removal of the poisoned part and interaction with the non-poisoned part of the targets. It also assumes a reactive diatomic molecule gas mixed with the sputtering inert gas (Ar for example) and that the molecules formed are diatomic with one metal atom and one reactive atom (for example AlO with O<sub>2</sub> gas). Extension to more complicated reactive molecules and a metal target is possible but more complicated to address [63]. A detailed description is provided in Ref. 63. A detailed description is provided in Ref. 63. Basically, at steady state, a fraction θ<sub>t</sub> of the target area A<sub>t</sub> is poisoned by the reactive gas, while 1 - θ<sub>t</sub> remains unaffected. It is thus assumed that removal of a compound is balanced by the formation of a target compound. On the other hand, part of the unreacted metal can be sputtered by the sputtering gas.

So the total sputtering yield Y = Y<sub>c</sub> + Y<sub>m</sub> with

$$Y_c = \frac{q}{JA_t} \alpha 2F \frac{1 - \theta_t}{\theta_t} \quad (8)$$

Y<sub>m</sub> is the yield of unreacted sputtered atoms given by the analytical formula (8) or available in the literature. 2F is the flux of reactive atoms (resulting from the dissociation of the corresponding reactive diatomic molecule) with  $F = \frac{P}{\sqrt{2\pi m k_B T}}$  and P is the reactive gas partial pressure, m the mass of the reactive molecule, T the gas temperature, k<sub>B</sub> the Boltzmann constant. J is the ion current density (J.m<sup>-2</sup>) at the magnetron target. Formula (8) assumes that the compound coverage is known. More complex situations such as multimetallic targets and multi reactive gases have been addressed, providing relatively simple formulae that can help to rapidly predict erosion rates and also deposition rates. Nevertheless, it should be borne in mind that these formulae result from crude approximations that do not take into account the many-body nature of the interaction with and inside the target.

### **3. Magnetron discharge modeling using Monte-Carlo simulations**

Many reviews and book chapters have addressed (reactive) magnetron plasma modeling [4,64-69] and articles have focused on specific issues, such as ion and neutral transport, erosion profiles of the target, reactive transport, magnetic field, ionization, etc. [70-112].

In Monte-Carlo (MC) simulations, computational test particles that represent a large number of real plasma particles are followed. They move due to the applied forces and collisions are included using

probabilities and random numbers. This technique is very easy to implement and fast to compute. Its main disadvantage is that the forces must be an input, i.e., the simulation is not self-consistent.


Many processes have been described using this technique: understanding of the transport and collision properties of the charged particles in magnetron discharges, effect of the magnetic field, ionization map in 2D simulations, ion motion, erosion profile of the target and its effect on magnetic field distribution [113 - 128]. The method can be implemented in 3D and can address magnetron sputtering reactors [129-134].

The plasma species obey the equations of motion in an ExB field [113,123]:

$$m \frac{d\vec{v}}{dt} = q(\vec{E} + \vec{v} \times \vec{B}) + \vec{F}_{coll} \quad (14)$$


$$\frac{d\vec{x}}{dt} = \vec{v} \quad (15)$$

with  $\vec{x}$ ,  $\vec{v}$  the position and velocity respectively,  $\vec{E}$ ,  $\vec{B}$  the electric and magnetic field, and  $\vec{F}_{coll}$  the collisional force accounting for momentum change. The collision term is calculated using the MC method. In a first attempt, elastic, excitation, and ionization collisions can be included. Elastic collisions lead to momentum change, while excitation and ionization collisions lead to energy losses. At each time step, it is determined whether a collision (between the electron and a nearby atom of the background gas) could occur. This is done by generating a random number, which is compared to the collision probability. Depending on the type of collision, the energy of the colliding electron is lowered to a specified amount. It can be reasonably approximated that the energy lost in an excitation or ionizing collision can be a fixed amount, 11.6 eV for excitation and 15.8 eV for ionization of argon. This defines the energy threshold at which the electron is effective. For ionization events, the kinetic energy of the emitted secondary electron is ignored, since this energy is almost always much smaller than the energy of the ionizing electron [135]. In addition to reducing the energy of the energetic electron when it undergoes a collision, its velocity is randomly chosen consistently with the corresponding differential scattering cross section. For energies  $E_e < 3$  eV, differential cross sections are assumed to be isotropic. For  $3$  eV  $< E_e < 3$  keV, tables of normalized values of  $d\sigma/d\Omega$  for elastic scattering [136] can be chosen. Figure 10 shows the distribution of ionizing electron collisions with Argon at  $P = 1$  Pa,  $V_b = -400$  V [113].

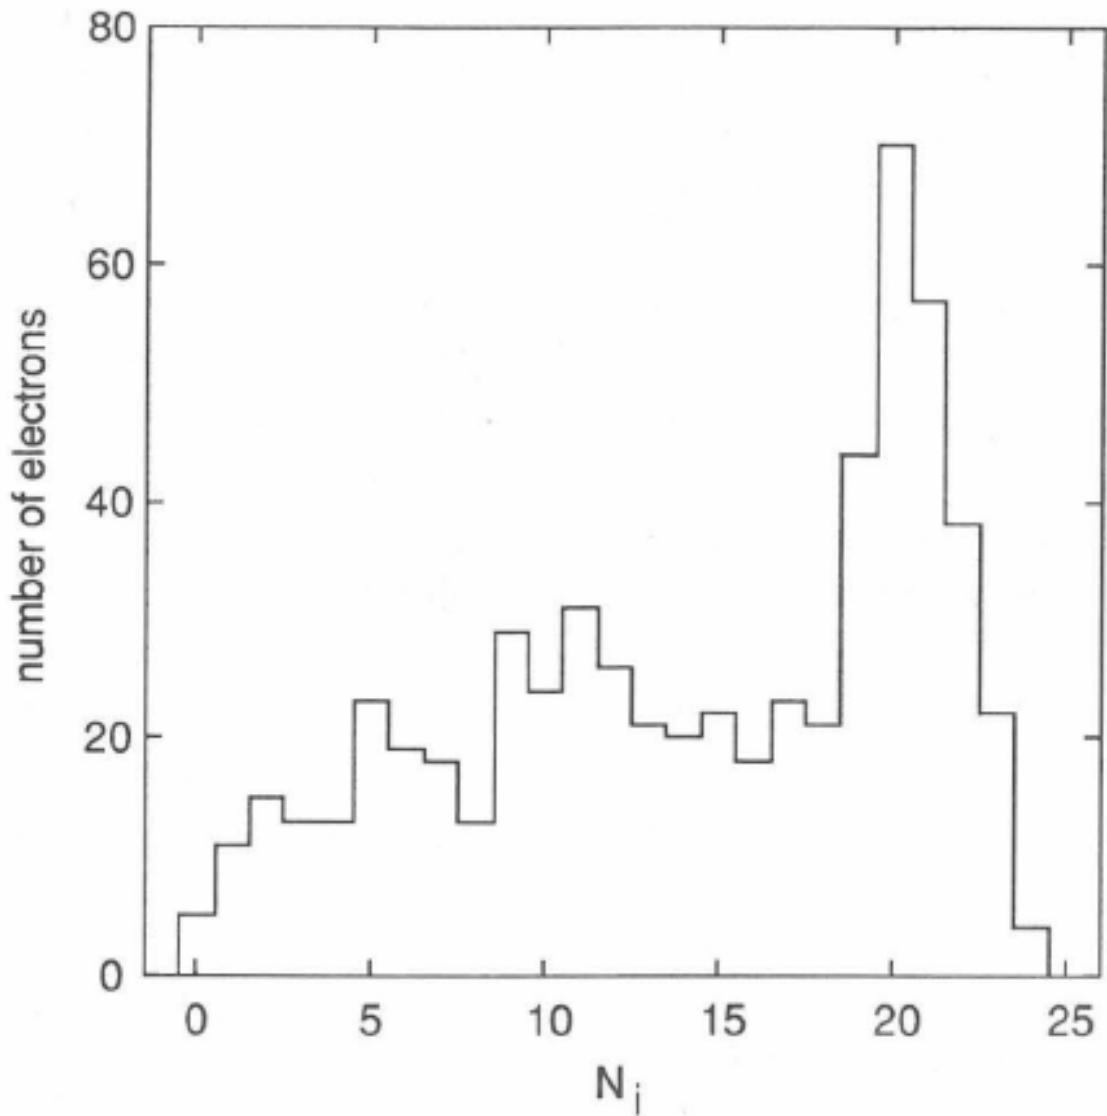

**Figure 10.** Distribution of number of ionizing collisions  $N_i$  for 600 electrons in argon at a pressure of 1 Pa. This histogram has a peak centered at 20 ionizations, which corresponds to electrons that lose all their energy in collisions without escaping from the magnetic trap. Elastic, excitation, and ionizing collisions are taken into account. The maximum possible number of ionizations is  $N_{\max} = 25$ , which is the ratio of the 400 V cathode potential to the 15.8 V ionization potential. The width of the peak is due to energy lost in excitation collisions. Reprinted from Ref. 113

The location of ionization is used to define the target racetrack, i.e. the zone where the ions normally sputter the target. In fact, Figure 11 shows the link between the etch profile of the racetrack and the ionization density above the target. It is important, therefore, to calculate this plasma parameter in order to determine and predict the target erosion.

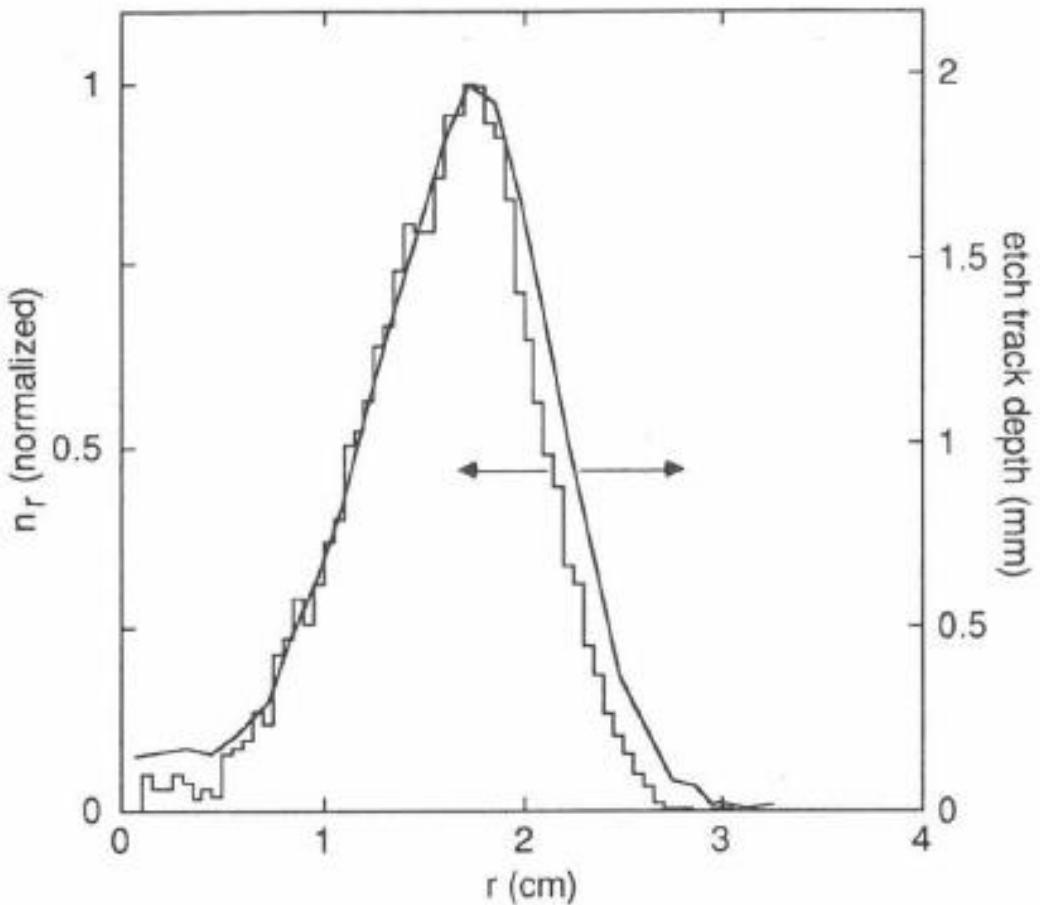

**Figure 11.** Radial profile of ionizing collisions,  $n_r(r)$ , from the simulation, compared to etch track depth from experimental measurements. The vertical scales for the two curves were adjusted to make the heights of their peaks match. The agreement is good. Reprinted from Ref. 113

A very powerful technique is PIC-MCC [137], which includes the calculation of the electric field produced by the external power source and the spatial distribution of the plasma charged particles in an MC simulation. The whole simulation thus becomes self-consistent. Since this topic deserves a review article in itself, the reader is advised to read the fully detailed reviews by Bogaerts' group [5, 67, 138] and the extensions to HiPIMS processes [105, 109].

MC simulations are also carried out to calculate the transport of sputtered materials from the target to the substrate as well as the growth of the resulting films. This is addressed in the next section, which also includes molecular dynamics simulations.

#### 4. Molecular Models of sputtering, transport and deposition

Since the processes of sputtering, (collisional) transport, deposition and growth are driven by atomic, molecular interactions, atomistic approaches are expected to be relevant.

#### **4. 1 Monte-Carlo models**


As stated above for electron motion in the discharge, collisions as well as neutrals can be handled statistically using Monte-Carlo models. The Monte-Carlo method [139 - 141] has also been successfully applied to sputtering [142-158] and sputtered material transport [159-175]. Kinetic Monte-Carlo simulations are able to address deposition and the resulting thin-film growth [176-195].

4 The most popular Monte-Carlo code of ion sputtering is the SRIM-TRIM [142] extended to multicomponent targets such as TRYDIN [143].


The impact of an incoming ion is treated using a binary collision approximation (BCA), which means that there are no many-body contributions and each collision includes only two colliding partners [145] without the memory of the past event: each collision is statically independent of the previous one. Each trajectory starts with a given position, direction, and energy of the ion. The ion is then followed through a sequence of collisions with target atoms, assuming a straight free travel path between collisions. Each collision lowers the particle energy by the amount of electronic energy loss and by the so-called nuclear energy loss, i.e. the energy transferred to the target atom in the collision. The target atom receiving an amount of energy which exceeds a preset value (e.g. the surface binding energy  $E_s$ ), is called a primary knock-on atom (PKA). Its motion and subsequent collisions will be followed in the same way as those of the incident ion. The same occurs with any higher generation of recoil atoms (SKA = secondary knock-on atoms), which are created after further collisions. The motion of an incident ion or recoil atoms is terminated either when the energy drops below a prescribed value (usually chosen as  $E_s$ ), or when the particle has moved out of the front or rear surface of the target. The target is considered amorphous with atoms at random locations, which means that any directional effects such as channeling are not considered here.

In three-dimensional space, initial conditions of the incoming ion are defined by velocity (kinetic energy) and angle of incidence and azimuthal angle, as displayed in Fig. 12, for example.

a) DIRECTIONS IN SPACE

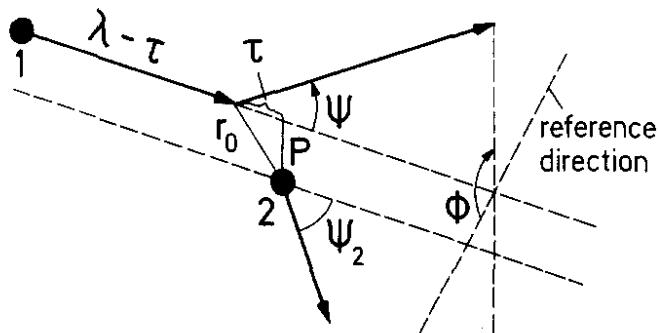

b) COLLISION IN THE C-M. SYSTEM (SCHEMATIC)

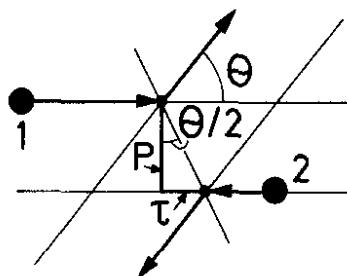

**Figure 12.** a) Directions of flight of projectile (ion or recoil) and of knock-on in 3-dimensional space. (b) Collision in the center-of-mass system (schematically drawn for a hard-sphere-collision).  
Reprinted from Ref. 142

The collided partner will move upon collision, and angles and velocities are selected in the appropriate distribution after selecting some random numbers. These quantities are calculated using the impact parameter  $P$  which defines the closest approach distance between the two collision partners via the relation:

$$1 - \frac{V(r_0)}{E_i} - \left( \frac{P}{r_0} \right)^2 = 0 \quad (16)$$

where  $r_0$  is the closest approach distance,  $P$  is the impact parameter,  $E_i$  is the kinetic energy of the incoming collider.  $V(r)$  is an interaction potential between the incoming ion and the target atom, chosen to be a repulsive screened Coulomb potential, such as Kr-C, ZBL, Molière, etc.

To define the output of the collision, the relevant parameters, impact parameter and angles, are randomly selected. The impact parameter is defined as  $P_{\max} = \pi^{-1/2} N^{1/3}$ , where  $N$  is the atomic density of the target material. A uniform random number  $R_p$  ( $0 < R_p < 1$ ) is selected such that the randomly selected impact parameter  $= P_{\max} \sqrt{R_p}$ . The center of mass deviation angle  $\theta$  is defined as,  $\cos \theta = \frac{P + \rho + \delta}{\rho + r_0}$ ,  $\delta$  being a small additional term [145]. The laboratory deviation  $\psi$  angle is defined as  $\psi = \arctan \left( \frac{\sin \theta}{\cos \theta + m_i/m_t} \right)$

Finally, the azimuthal angle is randomly chosen as  $\varphi = 2\pi R_a$  ( $0 < R_a < 1$ ). The energy  $E_f$  after the collision (in the center of mass) in a binary collision (Fig. 12) is:

$$E_f = E_i \frac{4m_i m_t}{(m_i + m_t)^2} \sin^2 \left( \frac{\theta}{2} \right)$$

The electronic energy loss is approximated by different functions depending on the energy range considered [143]. At the low ion energy of interest in magnetron sputtering, the electronic energy loss  $\Delta E_e$  is written:

$\Delta E_e = kE_i^p$  with  $p = \frac{1}{2}$  and  $k$  the Lindhard-Scharff [196] formula:

$$k = k_l = \frac{1.212 Z_i^{\frac{7}{3}} Z_t^{\frac{3}{2}}}{\left( Z_i^{\frac{2}{3}} + Z_t^{\frac{2}{3}} \right)^{\frac{2}{3}} m_i^{\frac{1}{2}}}$$

In this way all the relevant parameters of the sputtered materials can be calculated: Velocity distribution functions, angle distributions, as well as implanted and backscattered ion parameters. The main limitations are the amorphous nature of material and the binary collision approximation. Moreover, the calculation of the sputtering yields does not take into account the history of the target, i.e., it is carried out with a virgin amorphous material and thus does not account for preferential sputtering (this is done by the TRYDIN-TRIM version [146]) nor for the effects of voids, implanted ions and any outermost surface, such as roughness.

Another popular code is the ACAT code [151-157] from Yamamura. It is based on a different way of calculating the successive collision events and makes use of the repulsive Molière potential for ion target interactions. Nevertheless, it is its fitted analytic formula that is widely used for the sputtering yield dependence on ion energy [155].

The TRIM and ACAT strategies aim at calculating the history of the incoming ions in order to determine sputtering features. Another way, which is more statistical, involves considering the statistics of the ejected species based on the experimental erosion profile of the target [158]. To define the initial position of the sputtered atoms, a radial distribution function of the ejection point  $F(r)$  is connected with the experimental erosion profile function  $f(r)$  (Fig. 13 (a)) as:  $F(r) dr = f(r) 2\pi r dr$


We thus calculate the quantity:

$$a_m = \frac{\sum_{n=1}^m F(dr \cdot n)}{\sum_{n=1}^N F(dr \cdot n)} \quad (17)$$

with  $dr$  being the radial spacing between points and  $N$  the total number of radial intervals. Then we search for a uniform random number  $\varepsilon_1 \in [0,1]$  which is compared to  $a_m$ :  $\varepsilon_1 \leq a_m$ . Thus, from the minimal value of  $m$  satisfying this relation, the sputtered atom initial radial position  $r = dr \cdot m - dr/2$  can be determined.

Fig. 13 (b) and (c) displays the radial distribution of sputtering position. We have a 2D coordinate system by including the azimuthal angle  $\varphi$  through a new uniform random number  $\varepsilon_2 \in [0,1]$  and  $\varphi =$

$2\pi\varepsilon_2$ , which gives the coordinates  $(r, \varphi)$ . Fig. (13d) provides the 2D positions of 200 positions on the target.

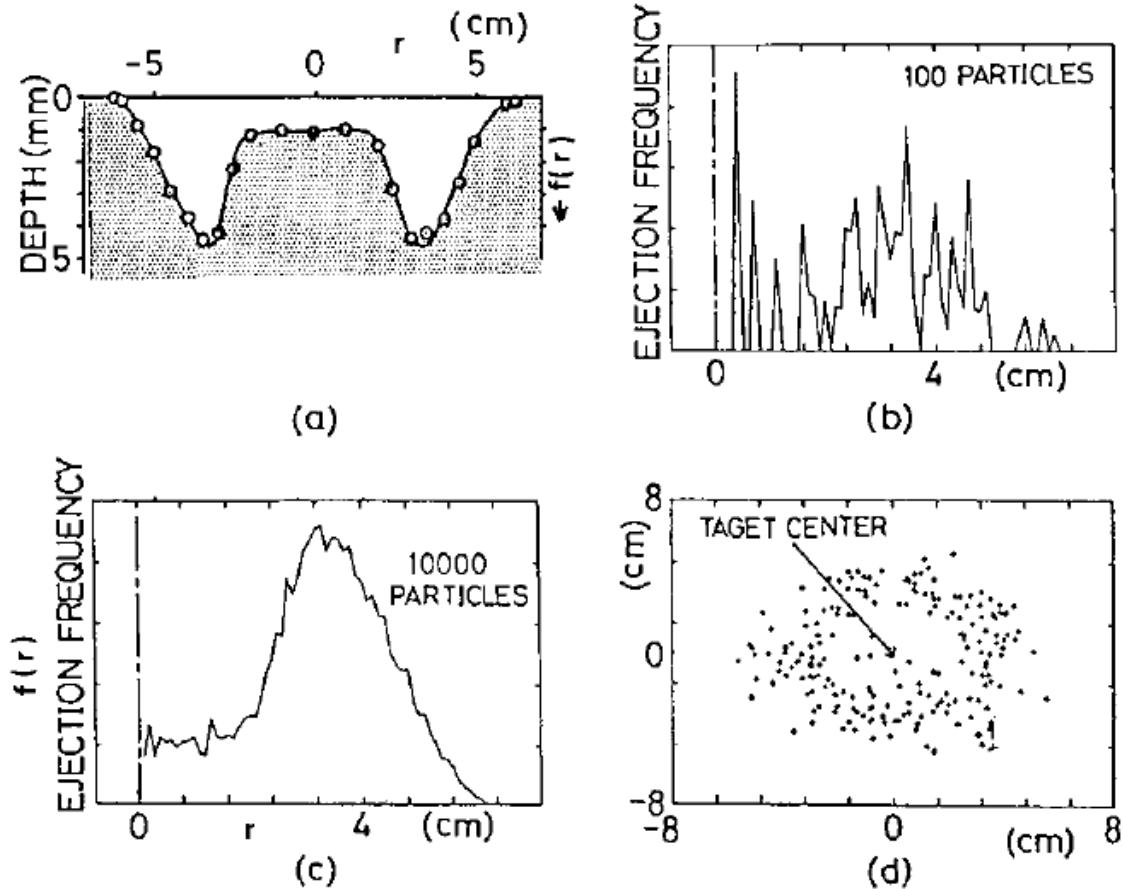

**Figure 13.** (a) Experimental radial erosion profile. (b) and (c) Distributions of computer-generated radial ejection positions of the first 100 and 10 000 particles using the experimental profile (a). (d) Two-dimensional computer-generated ejection points of the first 200 particles on the target.

Reprinted from Ref. 158

At this position  $(r, \varphi)$ , it remains to find the ejection angles. This is achieved by considering an ejection angle distribution for the direction normal to the surface and the azimuthal angles  $\theta$  and  $\phi$ , respectively. Uniform random numbers  $\varepsilon_3$  and  $\varepsilon_4 \in [0,1]$  are selected. When  $\theta$  obeys a cosine law, i.e.

$$\frac{P(\theta)d\theta}{2\pi \sin \theta d\theta} = C \cdot \cos^\gamma \theta, \text{ then } \theta = \cos^{-1}\{\varepsilon_3^{1/\gamma+1}\}.$$

The azimuthal angle is selected by  $\phi = 2\pi\varepsilon_4$ . It should be pointed out that this technique is dependent on the local surface geometry of the target and thus is extended to consider rough surfaces [88,90].

#### 4.1.2 Transport of sputtered species.

When sputtered atoms are emitted, they have to travel the target to substrate distance  $d$ , and depending on the pressure  $P$ , they have some probability to collide with plasma/gas species. The mean free path  $\lambda$  gives the distance between 2 collisions and is expressed as [162]:

$$\lambda^{-1} = 4\sqrt{2}\pi \frac{P_T}{kT} r_t^2 + \pi \frac{P_g}{kT} (r_t + r_g)^2 \left(1 + \frac{m_t}{m_g}\right)^{1/2} \quad (18)$$

with  $P_T$  and  $P_g$  the partial pressure of the sputtered target and gas atoms, respectively.

$m_t$  and  $m_g$  are the corresponding masses,  $r_t$  and  $r_g$  the corresponding atomic radii.

Since  $P_T \ll P_g$ , the first term in Eq. (18) vanishes. Moreover, the mean free path is energy dependent: an empirical fit suggests that  $\lambda$  should be multiplied by a factor  $E^a$ , with  $a = 0$  when  $E < 1\text{eV}$  and  $a = 0.29$  when  $E > 1\text{ eV}$ , leading to:

$$\lambda = E^a / \left( \pi \frac{P_g}{kT} (r_t + r_g)^2 \left(1 + \frac{m_t}{m_g}\right)^{1/2} \right)$$

Between two collisions, the travel distance  $\lambda^*$  of sputtered atoms is randomly chosen using a Poisson distribution:  $\lambda^* = \lambda \ln [1/(1-\varepsilon_5)]$ , with  $\varepsilon_5$  a uniform random number in  $[0, 1[$ . The next step is to determine the scattering angle  $\theta_{com}$  and the energy loss of the sputtered atom. In the center of mass frame, and for a spherical atom-atom pair interaction, the scattering angle  $\theta_{com}$  reads:

$$2\theta_{com} = \pi - 2b \int_{r_0}^{\infty} \frac{dr}{r^2 \{1 - [V(r)/E_{com}] - (b^2/r^2)\}^{1/2}} \quad (19)$$

and  $r_0$  is defined as  $b^2 = r_0^2 \left(1 - \frac{V(r_0)}{E_{com}}\right)$  (similar to Eq.21).  $B$  is the impact parameter lying between 0 and  $b_{max}$ .  $b_{max}$  defines the smallest deviation angle, which is arbitrarily defined, for example corresponding to  $\theta_{com} \leq 0.286^\circ$  [162].  $b$  is selected as  $b=b_{max}\varepsilon_5$ , with  $\varepsilon_5$  a uniform random number in  $[0, 1[$ .

$V(r)$  is the interaction potential between the sputtered atoms and the gas atoms. It is often chosen as a repulsive form such as Molière, Kr-C, ZBL, etc interaction potentials [47] of the form

$$V(r) = \frac{Z_t Z_g e^2}{r} g(r)$$

Where  $g(r)$  being a screening function.

The polar scattering angle  $\theta_{lab}$  in the laboratory frame is calculated as:

$$\theta_{lab} = \tan^{-1} \left( \frac{\sin \theta_{com}}{\cos \theta_{com} + m_T/m_g} \right)$$

while the azimuthal angle  $\phi_{lab}$  is randomly selected between 0 and  $2\pi$ . After collision with a gas atom, the sputtered atom energy loss is written:

$$E_{newlab} = E_{lab} \left( 1 - \frac{2(1 - \cos \theta_{com}) m_g m_T}{(m_g + m_T)^2} \right)$$

The energy loss is calculated until the sputtered particle reaches the substrate. Moreover, the kinetic energy of the sputtered particle is compared to a prescribed mean kinetic energy corresponding to the gas temperature. When it occurs, the sputtered particle is considered as thermalized and continues with this energy until it reaches the substrate. This procedure should be built while preserving a Maxwell-Boltzmann energy distribution at the gas temperature  $T_g$ . One way to achieve this is by randomly selecting the corresponding energy. Another way is to convolute the calculated energy distribution with the Maxwell-Boltzmann gas energy distribution [51, 52].

Since the sputtered atoms approach the substrate with a defined energy distribution function, a growth model can be designed.

#### 4.1.3 Kinetic Monte-Carlo growth models.

Kinetic Monte-Carlo growth models aim at simulating growth phenomena from a prescribed list N of possible events with an occurrence probability based on known rate constants  $k_i$ ,  $i=1, \dots, N$ .

Moreover, this method is able to calculate the time interval of the event realization by selecting a


uniform random number  $\epsilon \in [0, 1]$ , such that  $\Delta t = -\frac{\ln \epsilon}{\sum_i k_i e^{-E_i/kT}}$ ,  $E_i$  being the barrier height of the

process i. This enables various processes, with different time scales, to be calculated simultaneously.

Thus, long time diffusion becomes accessible. Reachable time lengths such as a few ms have been reported. In fact, there is no time limit since it depends only on reaction rate magnitudes.


Many data are required in order to build a kMC model. All possible or selected events should be recorded in a first step. For example, the growth may originate from a vapor of n different species with fraction  $\alpha_i$ , a flux  $F_i$  towards the substrate surface and a sticking probability  $s_i$  and  $E_{ik}$  barrier to process k. The method requires that the placement of the atom be predefined on a 3D grid that defines the expected crystalline positions. The crystal structure of the deposit or the surface does not necessarily have to be prescribed. The deposition of amorphous films can be achieved by randomly deforming the bond lengths and angles of a predefined structure [188].

Adsorption, and the motion on the surface or on the growing film or cluster, on the surface hence becomes a competition between the various processes, with  $E_{ik}$  the energy barrier defining the rate  $k_i$  and thus the probability of an attempt to move to the next position [177]. A possible flow chart [117] displayed in Fig. 14, describes the simulation steps.

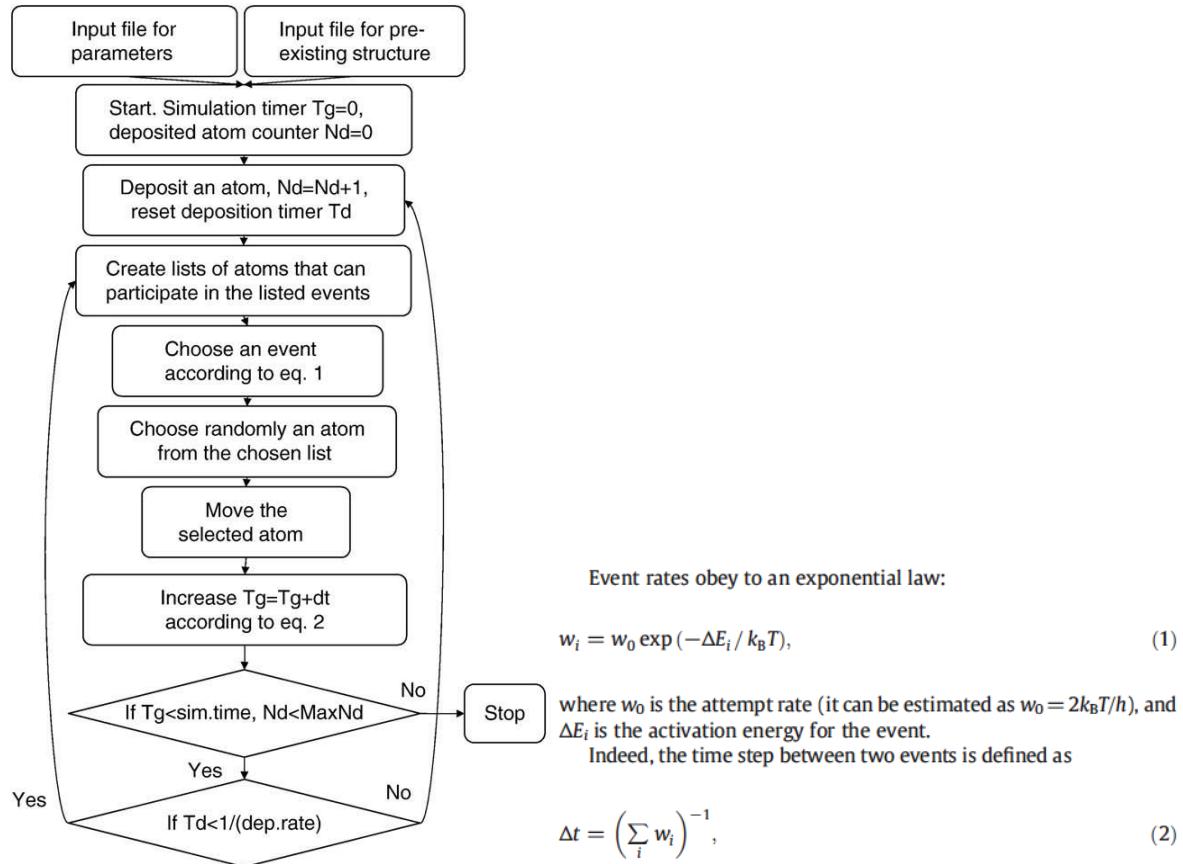


**Figure 14.** (Left) Flow chart of the NASCAM model; (Right) Eq. 1 and 2 from Ref. 177. In this case, the time interval is not sampled from a Poisson distribution. Reprinted from Ref.177

This method has been successful in reproducing (thick) thin film or cluster structure, composition and morphologies. For example, complex porous structures have been obtained and compared to experiments [189]. The origin of the growth of porous film has been elucidated using kMC and comparison with experiments (Fig. 15 and Fig. 16).

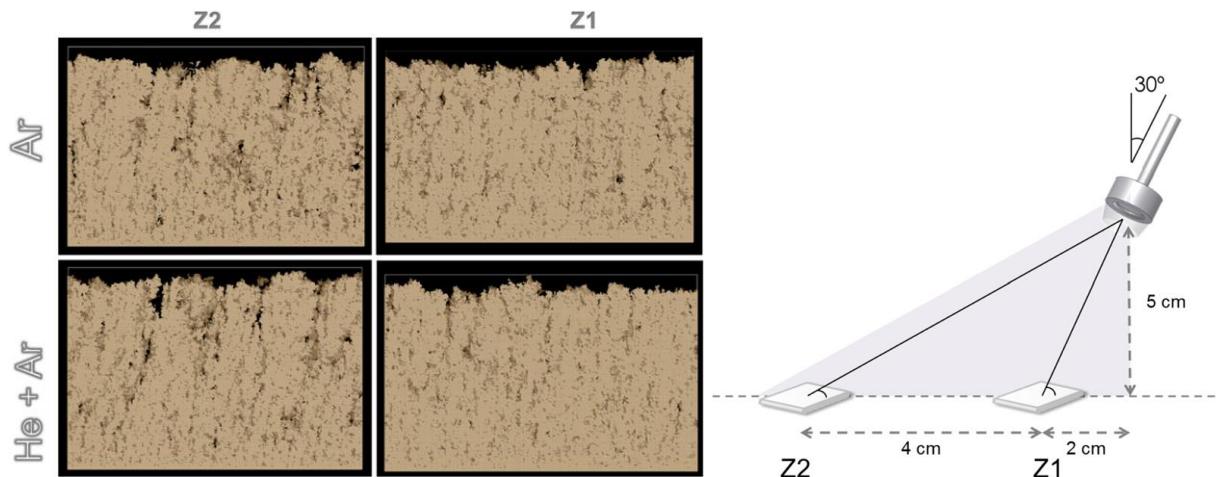


**Figure 15.** (left) kMC simulations of the growth at different deposition angles with different plasma compositions Ar and He + Ar. (right) positions Z1 and Z2 of the corresponding experimental setup defining the deposition angle. Reprinted from Ref. 189

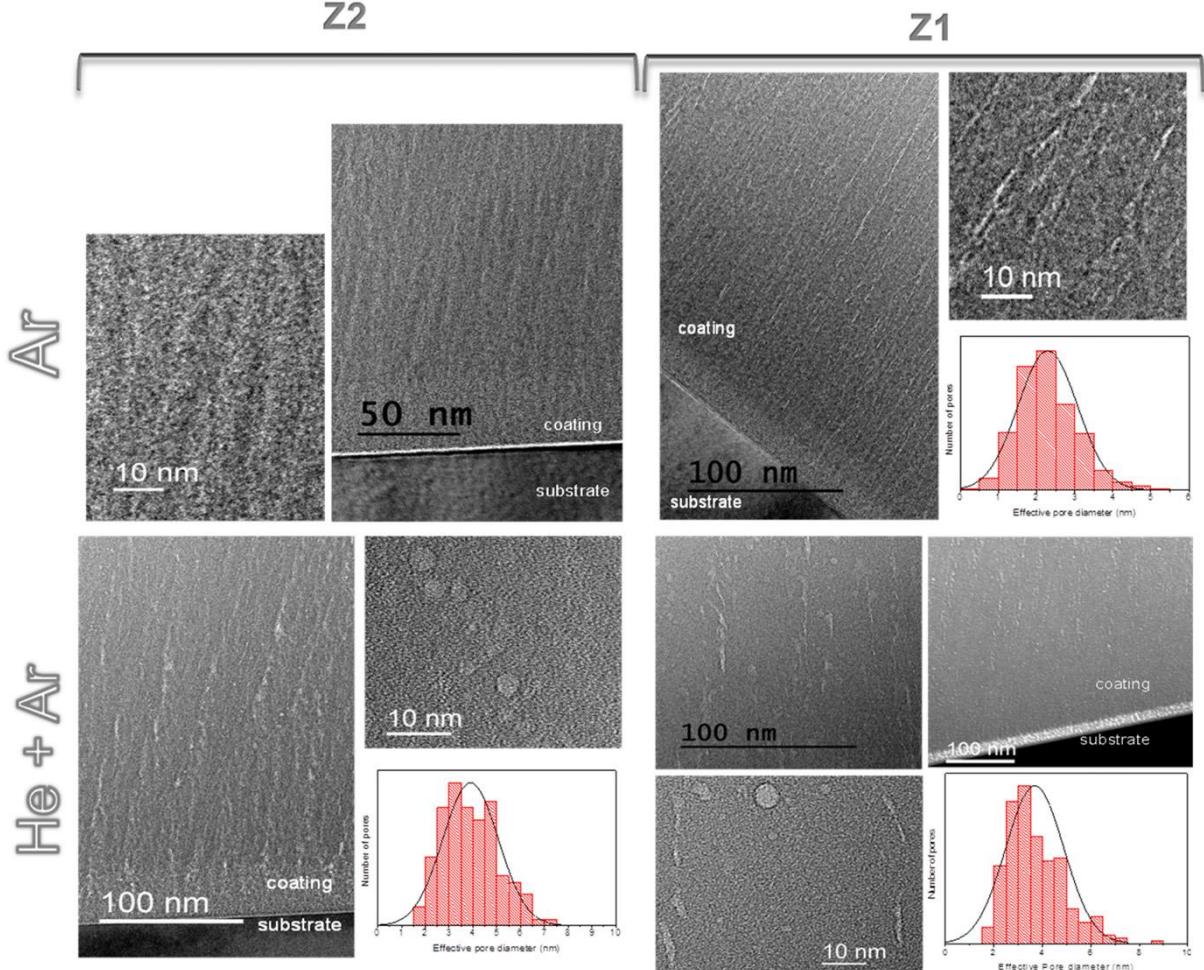

**Figure 16.** The Transmission Electron Microscopy pictures corresponding to kMC on Fig. 15, with porosity size distribution [Reprinted from Ref. 189].


On the other hand, reactions between species can be similarly included to simulate the growth of nitride, carbide, and oxide films [192, 193]. For example, the growth of a TiN film is simulated by fixing the possible places of Ti and N of a cubic B1 (NaCl-type) structure with a bulk lattice parameter  $a_0 = 0.424$  nm. The possible events are summarized in Fig. 17 [192]:

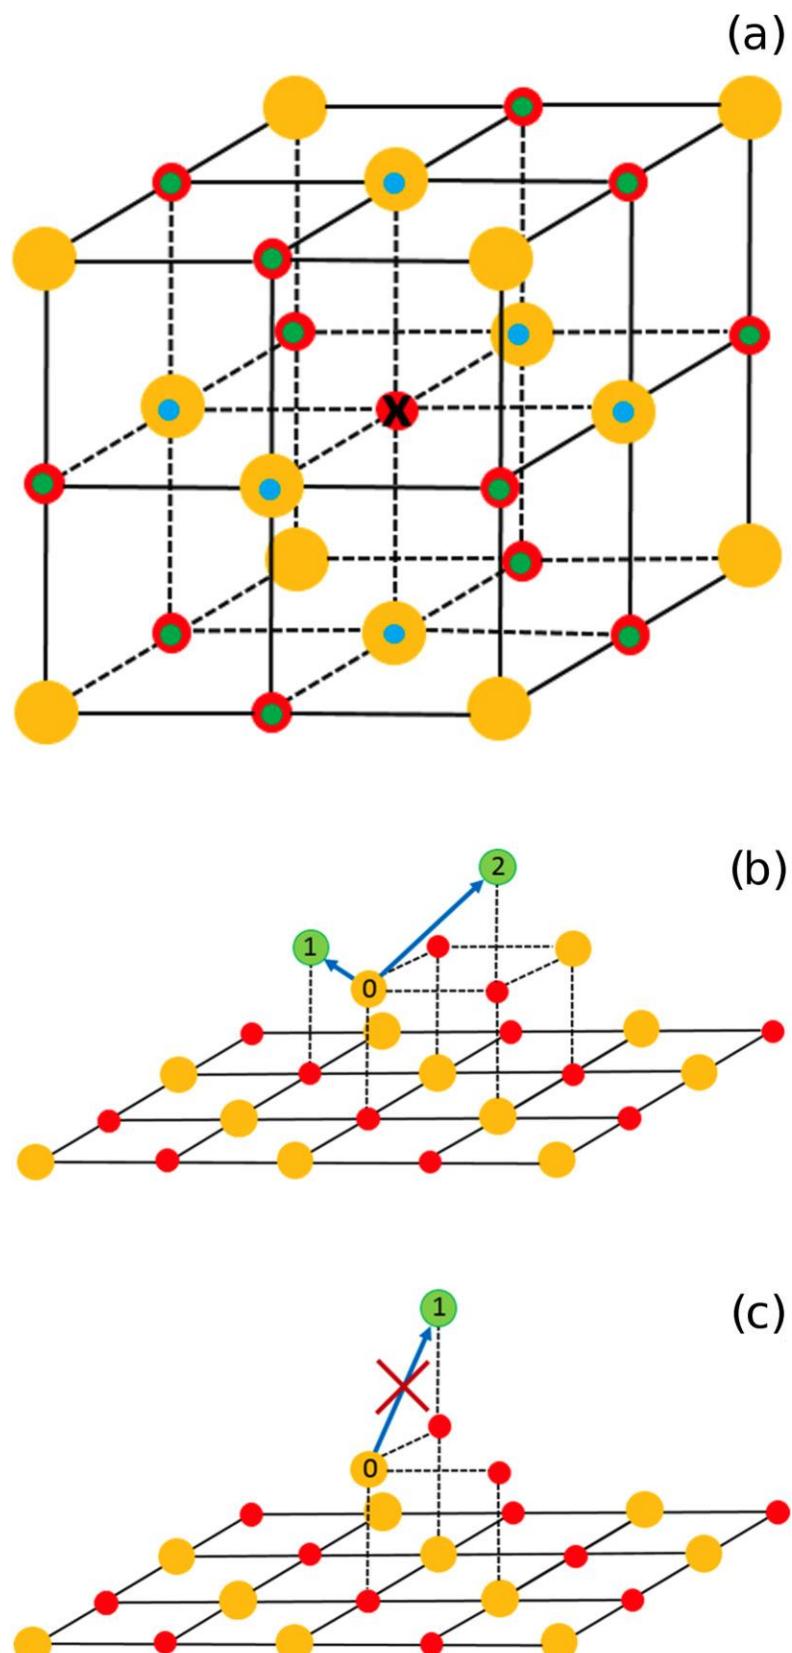

**Figure 17.** (a) Representation of the NaCl-type lattice cell of TiN: Ti atoms (large yellow spheres) and N atoms (small red spheres) occupy their own fcc sublattice positions. Two possible final sites (b) and a forbidden final site (c) for a diffusing Ti atom. Reprinted from ref.192

In this case, the total energy is calculated by considering interactions (barrier heights) of the nearest (Ti-N neighbors) and next nearest neighbor atoms (Ti-Ti and N-N neighbors). The energy values for different possible configurations are calculated and the lowest one defines the occupied site.

This procedure allows the growth of TiN thin films to be studied, and various film structures can be compared with Scanning Electron Microscopy (SEM). Two models, implementing two different ways for estimating energy barriers, were considered, leading to different film densities (Fig. 18).

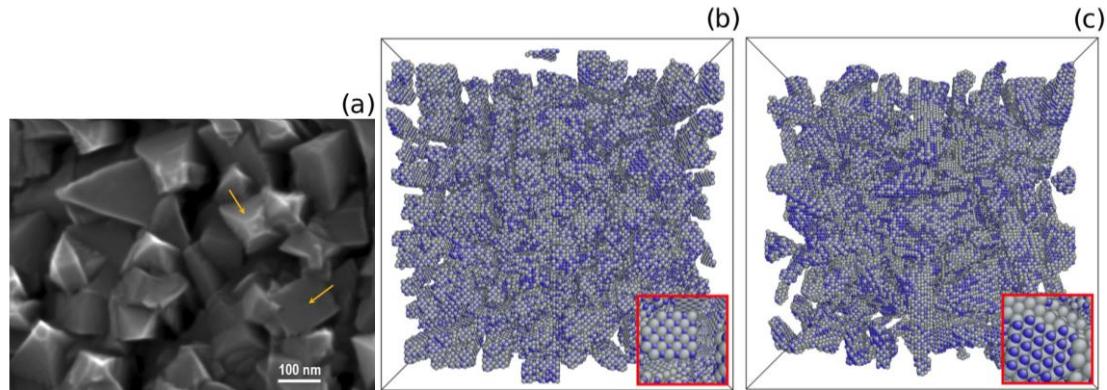

**Figure 18.** Top-view SEM micrograph of a magnetron sputtered TiN film at 750 K (a), exhibiting faceted columns (arrows indicate local surfaces with either fourfold or threefold symmetry), compared with kMC simulation results obtained using two diffusion models. Insets in (b) and (c) are taken along the normal of the local surface, corresponding to (001)- and (111)-oriented surface..

Reprinted from Ref. [192]

kMC approaches are very powerful for describing growth in various conditions due to their flexibility in including various phenomena that may occur on different scales. They can address very large sized systems up to reactor scale [162]. The main limitation is the *a priori* knowledge of the different event rates that is necessary to run a kMC code. Such input data can be obtained by molecular models such as Quantum Chemistry (QC) approaches, among which Density Functional Theory is a flexible version dealing with different approximations aiming at reducing computational resources (time and memory requirements). Nevertheless, the computational cost is always very high. Fortunately, Molecular Dynamics simulations bridge the gap between the mesoscale (MC/kMC) and the molecular level of QC methods and open the way to successfully describing magnetron sputter deposition.

#### 4.2 Molecular dynamics models

In Molecular Dynamics (MD) simulations, the evolution of a system of N atoms (more generally species) is followed at the atomic/molecular level by solving the Newton equations of motion [197-202], in the general form:

$$m_i \frac{d^2 \vec{r}_i(t)}{dt^2} = \vec{F}_i = -\nabla V(\vec{r}_1(t), \vec{r}_2(t), \dots, \vec{r}_N(t)) \quad (20)$$

where  $\vec{r}_i(t)$  is the position of atom i at time t with mass  $m_i$ , and  $V$  is the interaction potential between all  $N$  involved species. These equations only require the knowledge of two initial conditions, positions, and velocities at initial time  $t = 0$ , and of the interactions between all species at every time. The initial positions refer to geometry/topology of particles at the beginning of the simulation. Velocities are (randomly) selected from a velocity distribution that is consistent with the phenomena under study, for example selected from a Maxwell-Boltzmann distribution, from any relevant velocity distribution obtained from experiment (mass spectrometry for example), or from any other simulations dedicated to determining velocity or kinetic energy distributions such as those described above. The most difficult part concerns the interactions. Often, force fields are defined in a semi-empirical functional form including pair interactions, three-body and many-body interactions [53, 197, 198, 203-208]. Comparison between different force fields has been conducted [206-208], but not extensively. Both the quality of the potential and the computer time required when using complex many-body and targeted phenomena drive the choice of the force fields. Moreover, very recently machine learning based force fields emerged in the field of sputtering studies [209].


Leapfrog and Velocity Verlet algorithms can be used [197, 198] to solve the equation of motion (20).

The latter ensures the lower numerical error propagation. It is assumed that positions  $\vec{r}_i(t)$ , velocities  $\vec{v}_i(t)$  and accelerations  $\vec{a}_i(t) = -\frac{\vec{F}_i(t)}{m_i}$  are known at time  $t$ , the velocities  $\vec{v}_i(t + \frac{dt}{2})$  at time  $t+dt/2$  can be evaluated by:  $\vec{v}_i(t + \frac{dt}{2}) = \vec{v}_i(t) + \vec{a}_i(t) \frac{dt}{2}$ . Next, the new positions at time  $t+dt$  can be estimated as  $\vec{r}_i(t + dt) = \vec{r}_i(t) + \vec{v}_i(t + \frac{dt}{2})$ . Accelerations at  $t+dt$   $\vec{a}_i(t + dt) = \vec{a}_i[\vec{r}_i(t + dt)]$  can be calculated and the velocities at time  $t+dt$  can be determined:  $\vec{v}_i(t + dt) = \vec{v}_i(t + \frac{dt}{2}) + \vec{a}_i(t + dt) \frac{dt}{2}$ . This is repeated at each time step.

Molecular dynamics simulations are used like Monte-Carlo based methods for sputtering [210-247], transport (to a lesser extent) [248-258], deposition and film growth [259-307].

The main interest is that there is no a priori prescription on the rate constant. In fact, MD is a tool for finding rates that can be input to MC methods. Such outputs will only be dependent on the force fields. When the force fields are analytically defined, even when many-body interactions come into play, the calculations are faster. Nevertheless, calculating force at each time step remains quite time consuming. Another limitation is that the high kinetic energies of both sputtering ions and sputtered atoms require very small timesteps in order to solve the Newton equations of motion, for instance

0.1 fs [197]. Therefore, nanosecond time calculations require  $10^7$  timesteps. A problem that arises in MD simulation is the huge species flux difference between experiments and simulation. Typical experimental values can be on the order of  $10^{15} \text{ cm}^{-2} \text{ s}^{-1}$ , i.e.  $10 \text{ nm}^{-2} \text{ s}^{-1}$  while for MD simulations, they are on the order of 1 ( $10 \text{ nm}^{-2}$ )  $\text{ps}^{-1}$ , i.e.  $10^{10} \text{ nm}^{-2} \text{ s}^{-1}$ . The use of high flux in MD results in a high energy release to the substrate. To avoid this, the target or substrate can be thermostated with a relaxation time on the order of a few ps, which corresponds to phonon relaxation in solids. Thus, between two impacts, the surface recovers its initial temperature or nearly so. By releasing atoms or ions at time intervals on the order of thermal relaxation times, high incoming fluxes can then be used. There are many ways for implementing thermostats in MD simulations, such as Berendsen, Nosé-Hoover, Langevin, etc. [230-233]. A simulation box is designed as follows: a periodic solid (liquid) is periodic in xy mimicking an infinite target/substrate and thick enough in the z direction to prevent diffusing species from crossing the sample. The first few layers at the bottom of the simulated solid (or liquid) are motionless so as to mimic infinite solids in the vertical direction and to prevent motion of the substrate/target in the z direction. An intermediate zone is thermostated, while a few top layers are left free to move. Finally, incoming ions of atoms start from a height above the surface that is slightly larger than the highest cutoff radius, allowing smooth entry in the interaction zone. An illustration of such a design is given in Fig. 19.

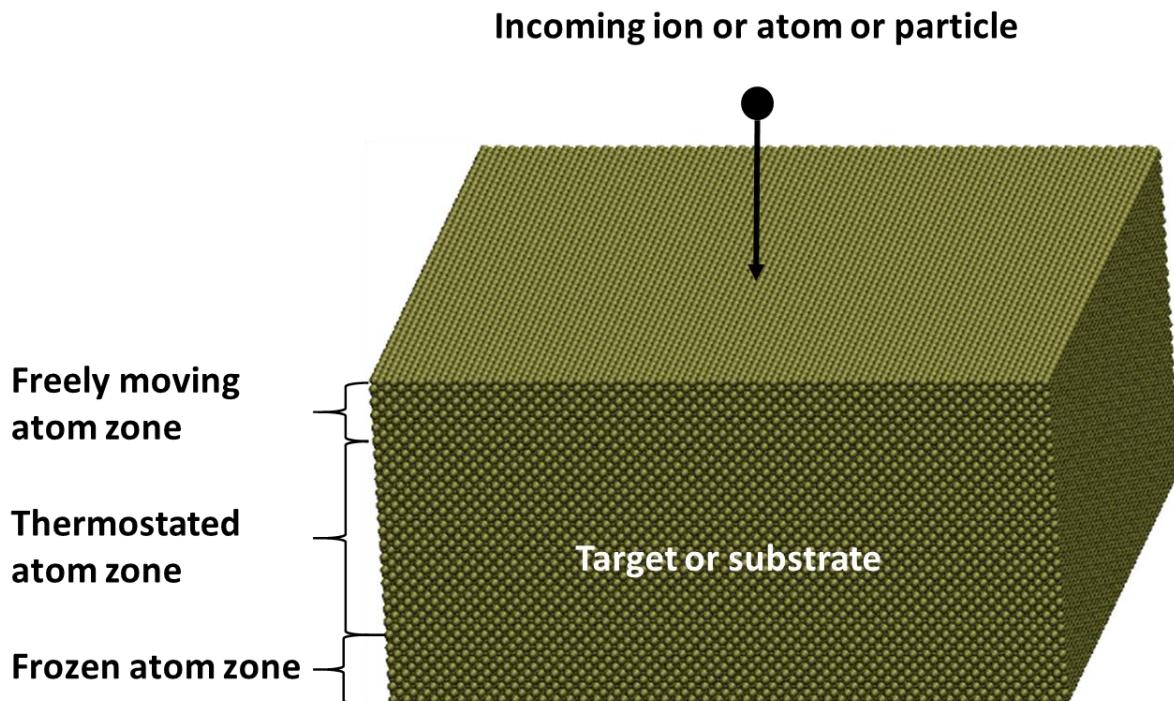


**Figure 19.** Initial configuration of the simulation. Small spheres are substrate atoms at the crystal position. Amorphous or liquid substrates are also possible. The incoming species are at random

location above the surface, and are directed towards the surface with any possible angle consistent with experiments.

#### 4.2.1 MD simulations of sputtering


MD simulations of sputtering are realized by releasing a statistically significant number of ions toward the target. In order to be as close as possible to the experiments, the ion positions are randomly selected above the simulated target, while velocities are deduced from the kinetic energy  $eV_b$ , where  $V_b$  is the cathodic fall potential at the biased target. These velocities can be normal to the target surface, but for a more realistic approach, a slight angle of incidence can be accounted for. Since ions are neutralized at the target surface, they can be treated as fast neutrals [240, 241]. Using the procedure described above, incoming ions will develop the collision cascade similar to Fig. 4. Thus, sputtering yields, retention rates and energy distribution functions can be calculated and compared to other models such as SRIM and theories. As illustration, Fig. 20 compares the energy distribution of sputtered Pt at different sputtering energies [241]. At high energy sputtering, MD simulations and SRIM are close since MD and the Thompson formula are closer at low energy sputtering.

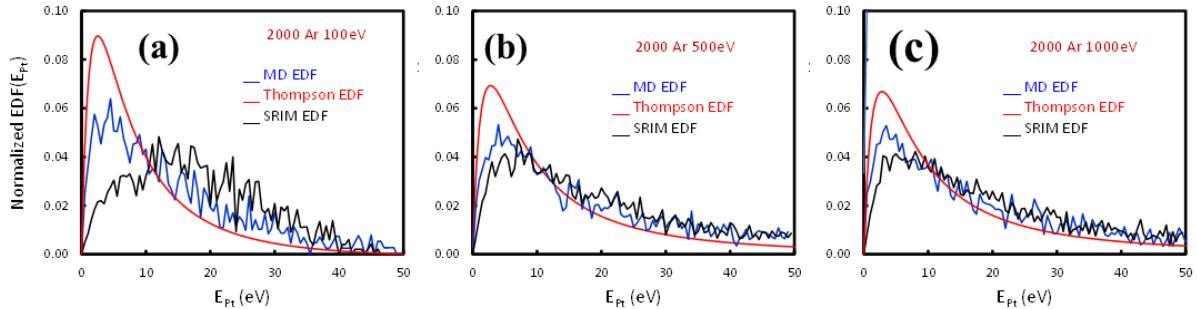

**Figure 20.** Energy distribution function (EDF) of the sputtered Pt atoms. Ar ion kinetic energy of (a) 100 eV, (b) 500 eV (c) 1000 eV. Reprinted from Ref. 241


Since SRIM always calculates the sputtering features with a virgin target, the differences with MD can be attributed to the fact that MD accounts for a material that evolves in the course of the sputtering. Since at high energy the two simulations are close, this means that the approximation of binary collisions in an amorphous solid is valid. Some specific phenomena have been addressed by MD such as preferential sputtering in alloys [244]: it is found that the lighter and the weaker bound species are sputtered preferentially. Retention of the sputtering ion in the target has drawn attention, especially for the application in Helium sputtering of fusion wall materials [240, 242 and references therein]. Helium implantation results in the growth of He bubbles that produce various surface morphologies

and structures induced by swelling and flaking. Moreover, it was found that MD simulations are consistent with experiments, regarding dose, energy and temperature effects. A typical incoming He energy and tungsten temperature dependence of the implanted He distribution is displayed in Fig. 21 [242]

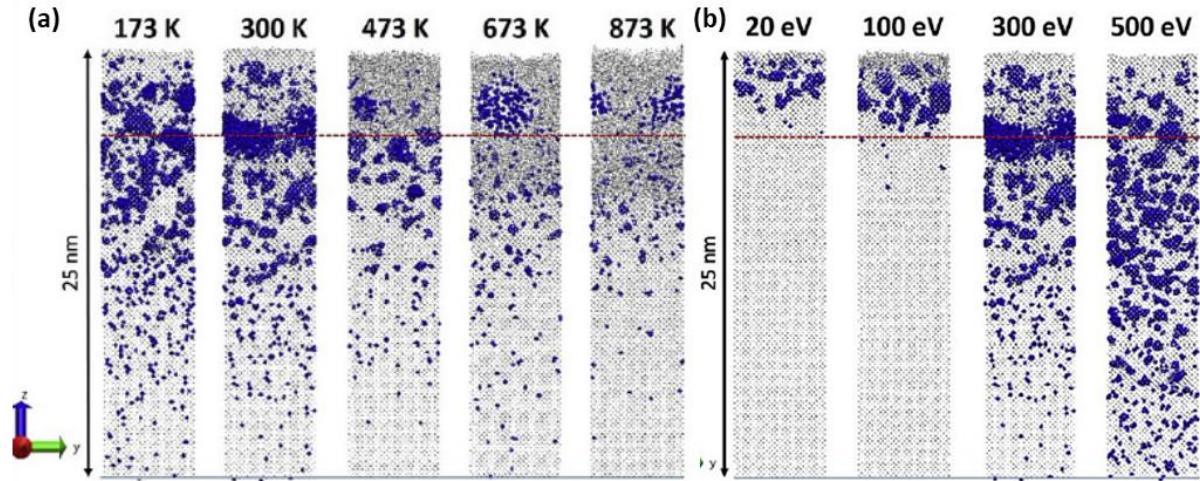

**Figure 21.** Tungsten target temperature (a) and He kinetic energy (b) effects on helium retention. Blue spheres are helium atoms and grey dots are W atoms. Dots were chosen instead of spheres at the right size ratio to better display helium organization. Reprinted from Ref. 242


The sputtering of complex (porous) materials [244-246] is also of interest since bombarding a soft material is expected to modify sputtering rates and sputtered species energy and angle distribution. A nanoporous structure increases sputtering rates due to local curvature effects, as shown in Fig. 22. Moreover the non-monotonic nature of the sputtering yields versus Ar dose is

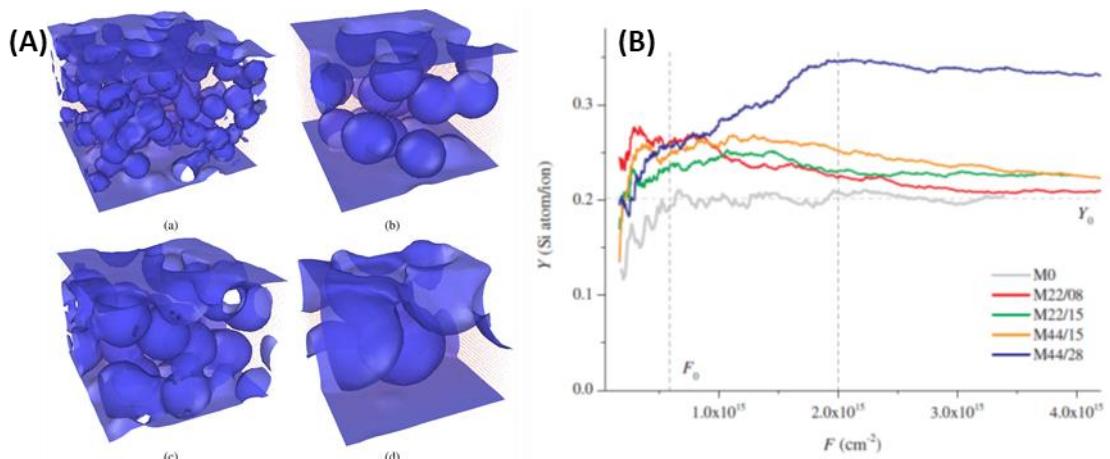

**Figure 22.** (A) 3D images of four models with different pore radii and porosity: (a) M22/08; (b) M22/15; (c) M44/15; (d) M44/28. The nanoporous structure of models is represented by blue

continuous surfaces. (B) Evolution of the sputtering yield by 200eV Ar of the four nanoporous Si samples compared to crystalline Si (M0). Reprinted from [246].

attributed to the morphology change in the porous structure, as shown in Fig. 23.

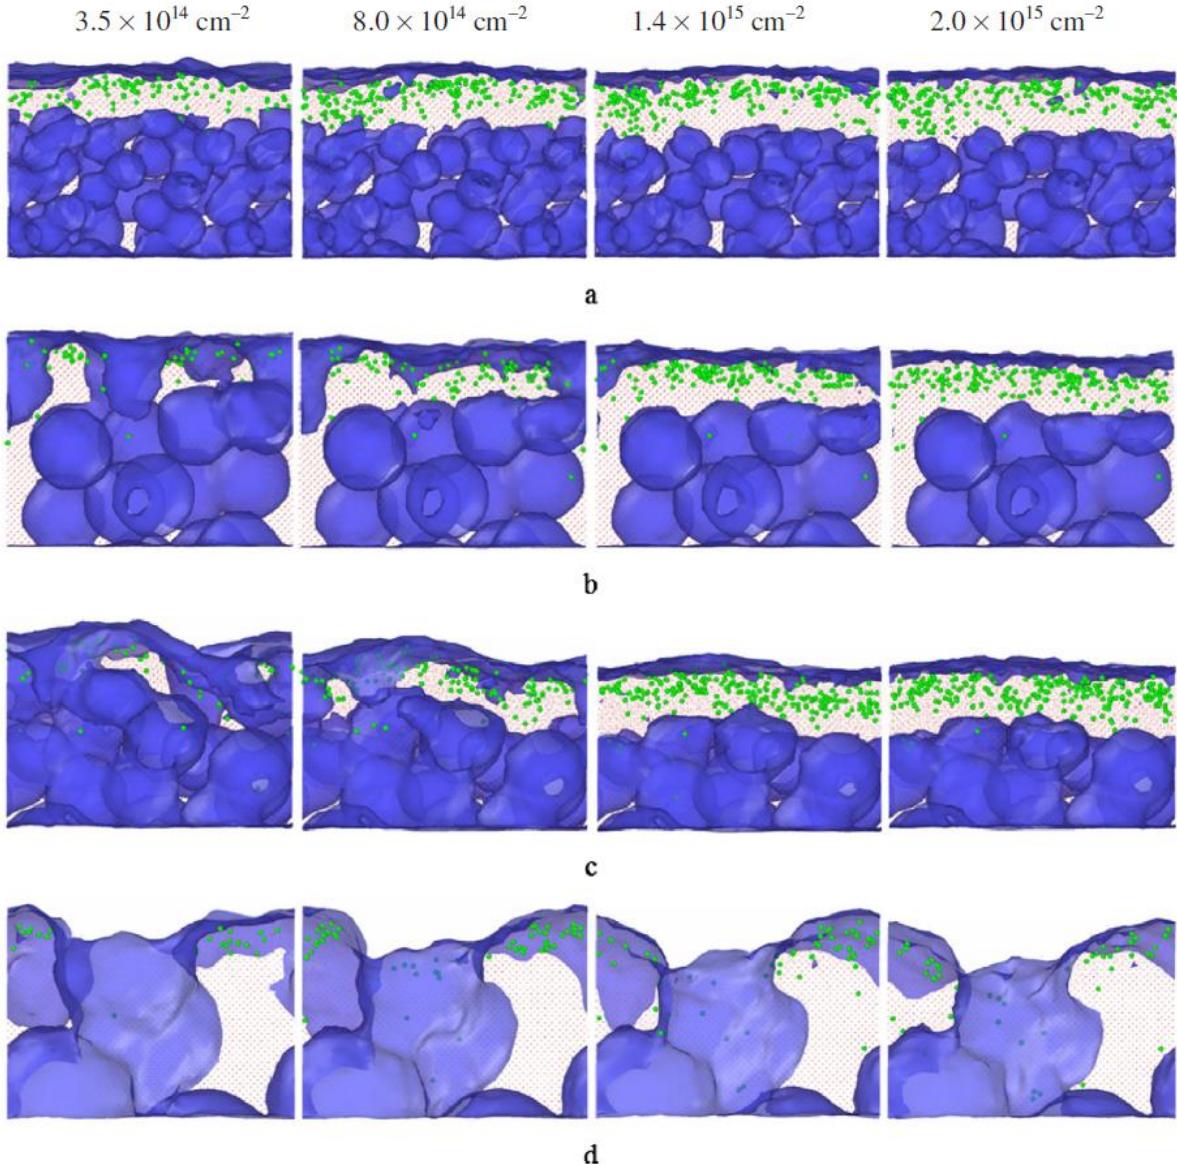

**Figure 23.** Side views of the nanoporous models obtained at different ion fluences (given on top of the figure): (a) 22% porosity and pore radius 0.8 nm; (b) 22% porosity and pore radius 1.5 nm; (c) 44% porosity and pore radius 1.5 nm; (d) 44% porosity and pore radius 2.8 nm. Implanted Ar atoms are shown with green circles, and blue surfaces represent the nanoporous structure. White areas represent the empty regions. Reprinted from Ref. 246.

#### 4.2.2 MD simulations of sputtered atom transport.

Simulating the transport of sputtered atoms using MD is not straightforward since the gas between the target and the substrate is highly diluted. A 1 atm gas gives a density of  $2 \cdot 10^{-2} \text{ nm}^{-3}$ . Assuming a  $10 \times 10 \times 10 \text{ nm}^3$  simulation box, there will be only 20 gas atoms in the simulation cell. Therefore, this cannot represent the reality of collisional transport to the substrate.

An alternative is to use an MC step as described in section 4.1.2 to determine the velocity of the sputtered atoms at the substrate surface and use it as an initial condition for a further MD simulation of the growth with these incoming atoms. A faster approach is to evaluate analytically the change in the sputtered atom energy distribution function when passing through a gas at temperature  $T_g$  and pressure  $P$  [51, 52, 235]. The final energy  $E_f$  of an atom travelling a distance  $d_{T-S}$  between the target and the substrate is given by:

$$E_f = (E - k_B T_g) \exp[n \ln(E_f/E_i)] + k_B T_g \quad (21)$$

$E_f/E_i = 1-\gamma/2$  is the ratio of energies after and before a collision,  $\gamma = 4 \frac{m_i m_t}{(m_i + m_t)^2}$  [52], and  $n = dP\sigma/k_B T_g$ ,

$\sigma$  being the collision cross section between the sputtered target atom and the gas atom.  $E_i$  is the energy of the sputtered particles as they leave the target,  $n$  is the number of collisions that take place in the gas,  $d$  is the distance travelled. To calculate the energy loss ( $E_f$ ) of sputtered atoms with the gas atoms during the flight towards the substrate, a Maxwell-Boltzmann (MB) distribution at  $T_g$  is used for the velocity distribution of the gas. Because we search for the complete energy distribution  $F(E_f)$  of sputtered atoms, for each  $E_g$  in the MB gas distribution, the energy loss is calculated for a fixed value of the kinetic energy  $E$  of a sputtered atom. This is repeated for each energy value of the distribution and weighted by the collision probability, which is simply the convolution of  $F(E_f)$  and the MB distribution at  $T_g$ . [51]. Initial kinetic energies can be obtained from such a distribution using a rejection method, and velocities can be deduced.

Another way is to scale down the reactor size to an MD simulation box. This is achieved by stating that the collision number along the travel path to the substrate in the simulation box is the same as in the experimental sputtering reactor [252, 257]. Equating the collision number in the simulation box (index sim) and in the reactor (index exp) leads to the relation

$$P_{exp} d_{exp} = P_{sim} d_{sim} \quad (22)$$

Note that the simulation box volume can be written as  $V_{sim} = S_{sim} d_{sim}$  where  $S_{sim}$  is the area normal to  $d_{sim}$ . If  $d_{sim}$  is along the z axis then  $S_{sim}$  is in the xy plane. Using  $P_{sim} = \frac{N_{sim}}{V_{sim}} \cdot k_B T_g$ , with  $N_{sim}$  being the number of atoms in the simulation box, Eq (22) can be rewritten as:


$$N_{sim} = \frac{P_{exp}}{k_B T_g} \cdot S_{sim} \cdot d_{exp} \quad (23)$$

which does not depend on  $d_{sim}$ . Nevertheless,  $d_{sim}$  can be calculated keeping in mind that the species in the gas/plasma phase should not be closer than the largest interaction cutoff  $r_{cut}$  used in the simulations. The distance  $l$  between gas/plasma phase species can thus be estimated as:

$$l = \left[ \frac{N_{sim}}{S_{sim} \cdot d_{sim}} \right]^{\frac{1}{3}} > r_{cut} \text{ and thus, } d_{sim} > \frac{N_{sim}}{S_{sim}} \cdot r_{cut}^3 \quad (24)$$

Therefore, the correct number of species in the simulation box can be deduced in order to match experimental conditions. This makes it possible to describe a full sputtering/transport/deposition on a substrate system using only MD simulations [252, 257].

Such an approach is relevant for the in-flight growth of nanoparticles during magnetron sputtering at high pressure in a gas aggregation source [248-258]. Such simulations have revealed the temperature evolution of the nanoparticles during growth as shown in Fig. 24. The ambient gas atom and the internal degrees of the growing nanoparticle share the excess bond energy of the growing nanoparticle. When the nanoparticles cease to grow, they are cooled by collision with the ambient gas, which is itself cooled by collision with the wall. This last step is simulated by thermostating the ambient gas with a relevant relaxation time.

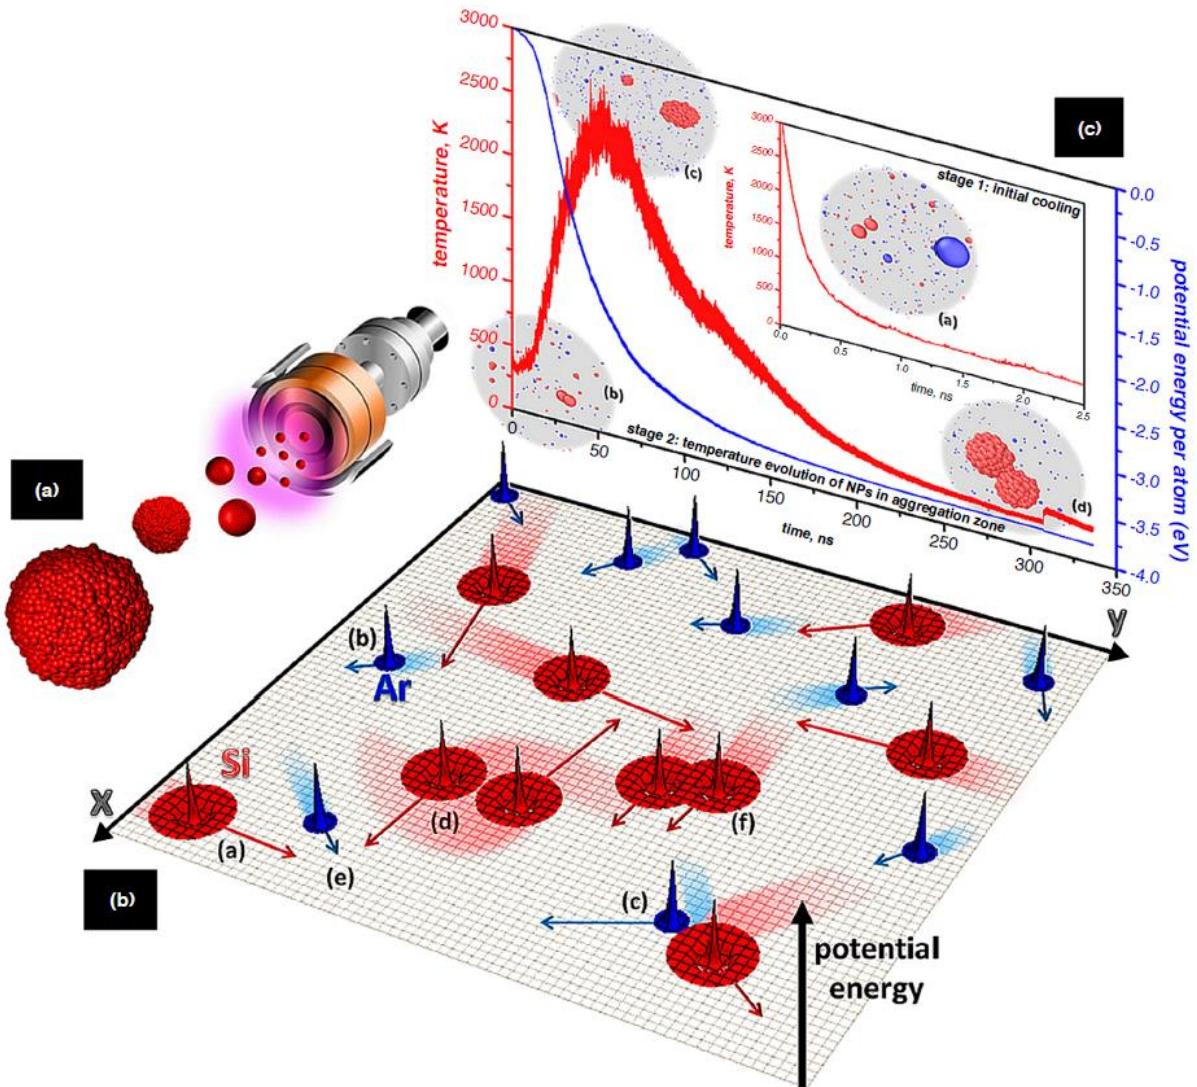

**Figure 24.** (a) Illustration of pure-Si cluster growth from a single-target magnetron-sputtering source. (b) Schematic representation of an MD simulation box, containing Si and Ar atoms, represented by red and blue potential energy functions (instances (a) and (b), respectively). Atom velocity vectors are indicated by arrows. Instance (c) depicts a Si and Ar system post-collision (note the velocity exchange, implying cooling of the Si atom and heating of the Ar atom). Instance (d) shows the temporary attraction of two Si atoms not resulting in bond formation. In contrast, instance (e) indicates an imminent three-body collision that may result in bond formation. Instance (f) depicts a stable Si dimer. (c) Temperature and potential energy evolution during nucleation and growth of a Si nanoparticle (500 Si and 1500 Ar atoms in the MD box). The inset focuses on cooling during the initial 2.5 ns. MD visualization snapshots designate four steps of the growth mechanism. Reprinted from Ref. 255

#### 4.2.3 MD simulations of sputter film growth.

The first MD simulations of plasma sputtering deposition started in the late 1980s in two dimensions and addressed the effects of suprathermal energies on film structures as well as internal stress [259-261]. They were quickly followed by 3D simulations from the beginning of the 90s, due to the increased capabilities of computers as well as the development of new many-body force fields (such as the embedded-atom method (EAM) and the modified embedded-atom method (MEAM) ), well suited for studying metal sputtering and deposition [204]. In the meantime, pair potentials such as Buckingham or three-body Vashishta and Stillinger -Weber potentials [198] were used to study oxide and nitride compounds. As already mentioned, the use of such potentials needs to be carefully analyzed in view of the effects to be interpreted. For example, a phenomenon depending on the charge transfer would require a variable charge force field [203], while working at high temperature would require checking that the potential parametrization included high temperature materials properties, etc.

Simulating growth from sputtered particles (atoms, molecules, clusters) using MD requires the definition of the simulation box and the gas phase above the substrate surface. The box should be large enough to avoid boundary effects and is often periodic in the directions parallel to the surface (xy). The simplest way to build an MD growth simulation is to prepare a vapor of particles above the surface with velocities directed towards the surface. These velocities can be simply normal to the surface with values corresponding to the expected kinetic energy. A more elaborate scheme would select the velocity in a refined velocity distribution, obtained, for example, from energy resolved mass spectrometry.


Since microstructure development and stress in films are widely studied in experiments, this has led to numerous numerical studies in the past decade. They have been studied versus incoming ion energy, composition (for alloyed films), and temperature, often with the goal of comparing with experimental measurements and linking the atomic scales of MD to the experimental micron scales of topographies [272].

The total stress value of the film can be deduced from MD simulation via the velocities and force evaluations [278, 302]:

$$\sigma_{ij} = -\frac{1}{V} \sum_{\alpha \in V} \left( M^\alpha v_i^\alpha v_j^\alpha + \frac{1}{2} \sum_{\beta \neq \alpha} F_i^{\alpha\beta} r_j^{\alpha\beta} \right), \text{ where } V = \sum_{\alpha} V_{\alpha} \quad (25)$$


where  $\sigma_{ij}$  is the i, j component of the stress tensor for atom  $\alpha$  ( $i, j = x, y, z$ ),  $V^\alpha$  is the atomic volume assigned to atom  $\alpha$ , and  $V^\alpha = 1/\rho$ ,  $\rho$  is the atom number density per unit volume.  $M^\alpha$  is mass ,  $v_i^\alpha$  is the i component of the velocity,  $v_j^\alpha$  is the j component of the velocity of atom  $\alpha$ .  $F_i^{\alpha\beta}$  is the i component of the force on atom  $\alpha$  due to atom  $\beta$ , and  $r_j^{\alpha\beta}$  is the j component of the separation of atoms  $\alpha$  and  $\beta$ .

For example, MD simulations of the growth stresses have been detailed as a function of various island textures, grain sizes, grain morphologies, deposition rates, and deposition energies [302]. Fig. 25 displays the various initial configurations for studying stress generation of the various microstructures.

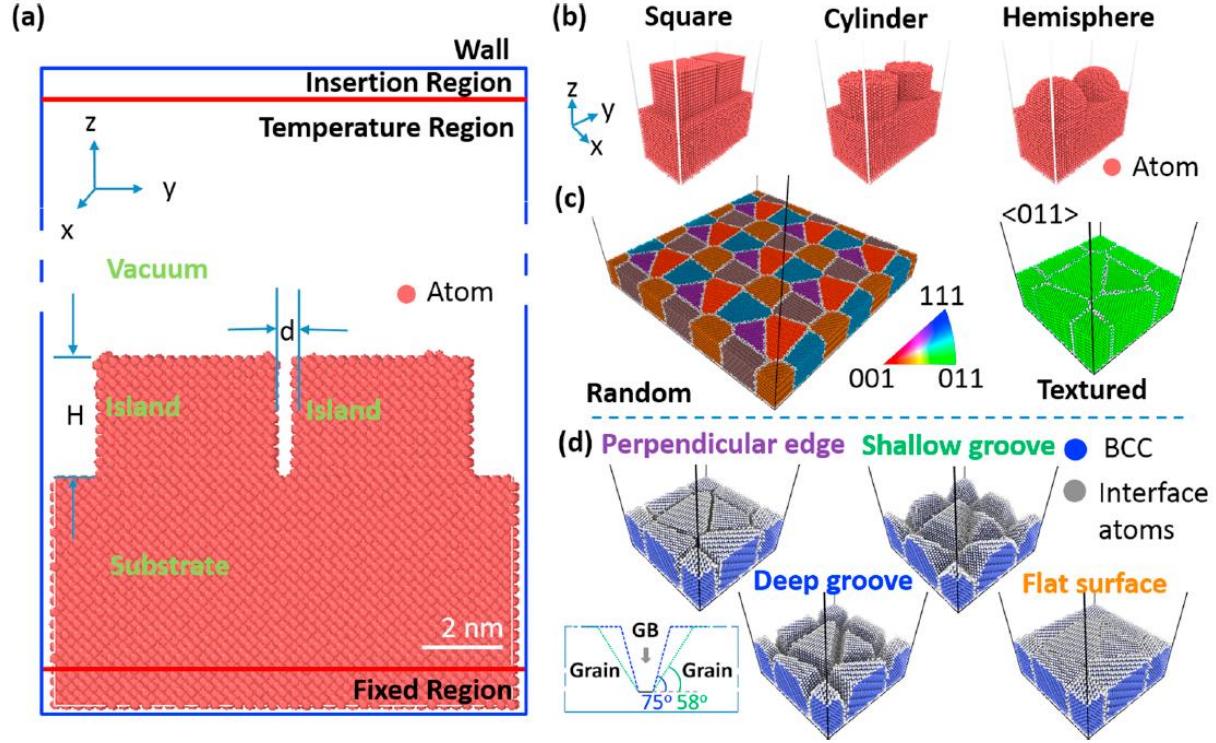


**Figure 25.** (a) A sketch of the MD model, (b) single crystalline island model, (c) polycrystalline island model with random and  $\langle 0\ 1\ 1 \rangle$  texture and (d) polycrystalline islands with different surface morphologies. The insert sketch helps the reader to find the slope of island grains for the deep groove model and the shallow groove model. The slope angles for the deep and the shallow groove models are  $75^\circ$  and  $58^\circ$ , respectively. Reprinted from Ref. 302.

Evolution of the stress is calculated using realistic polycrystalline film. The elastic strain across multiple faces leads to a more homogeneous deformation. The stress state of the film is influenced by the surface morphology (Fig. 26).

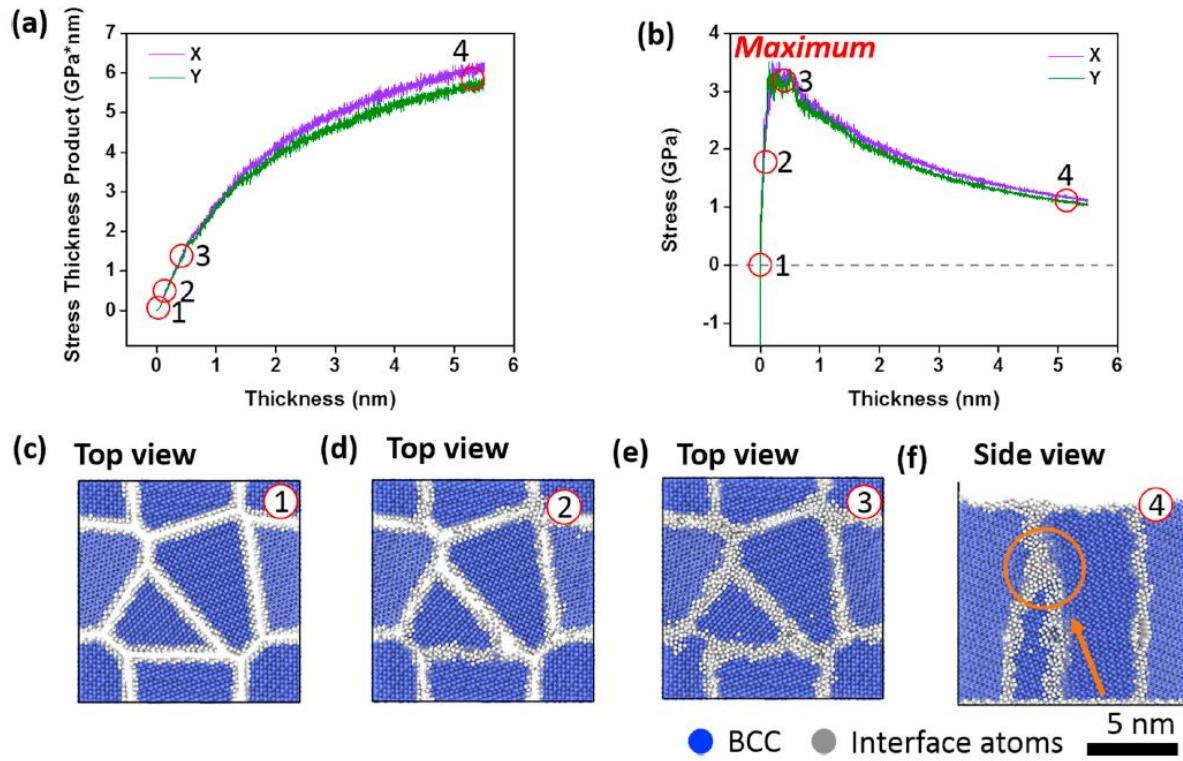

**Figure 26.** (a) Stress and thickness products; (b) Stress varying with film thickness when 5 eV tungsten atoms are deposited onto the surface of a perpendicular edge island; (c)-(e) Three 2 nm top view slices, near the surface of the substrate were chosen to show the coalescence process. (f) One 2 nm side view slice to illustrate grain growth during deposition. The numbers represent the position where the slices were selected to calculate plots (a) and (b). Reprinted from Ref. 302

Incoming atoms with higher energy transfer momentum into the film. This is known as an atomic peening effect, which induces a reduction in tensile stress or the generation of a compressive stress. The latter occurs for energies above 50 eV and for film thicker than 1 nm, as shown in Fig. 27.

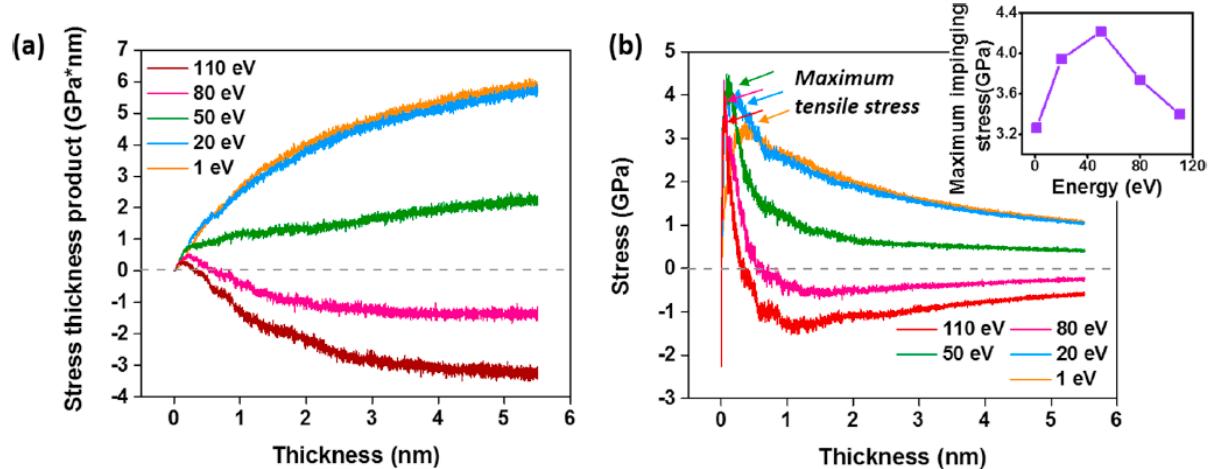


**Figure 27.** (a) Stress and thickness products and (b) stress varying with film thickness when 1 eV, 20 eV, 50 eV, 80 eV, and 110 eV tungsten atoms deposited onto the surface of a perpendicular edge islands. The maximum impinging tensile stress for different injection energies are plotted in inset in (b). Reprinted from Ref. 302.

Such a study is a very significant contribution to understanding the basic mechanism of microstructure and stress generation. More generally, this methodology can be easily reproduced for any thin film. Moreover, the use of free and well documented LAMMPS software [308, 309] allows such mechanical simulations. The question that arises is the relevant box size needed for meaningful results that can be compared to experimental scales.


Multimetallic alloys have gained growing interest and among them high entropy alloys (HEA) have been investigated [310] due to their wide range of applications. They are also widely studied using MD since robust force fields are available, thus allowing direct comparison with experiments. They are also interesting modern techniques for high throughput simulations and developments based on machine learning (ML) models [310, 311]. ML techniques, and more generally Artificial Intelligence (AI), are intended to develop a data-based strategy to predict the structure, microstructure and properties of alloys which could minimize the number of experimental trials for alloy development. On the other hand, there is a great need of interaction potentials for oxide, nitride and carbide forms of HEA and ML and AI will certainly be called upon to play a central role in developing relevant interaction potentials. This will, in turn, enable MD and MC simulations of interest to be carried out for direct comparison to magnetron sputtering deposition simulations.

Composition effects, the kinetic energy of incident atoms, and temperature are parameters that are studied to determine the evolution of microstructure, morphologies, etc.


Fig. 28 to 30 display the compositional effect on the microstructure evolution of HEA AlCoCrCuFeNi thin film alloys. When Al is the only low content element, the microstructure evolves from amorphous to crystalline during growth. At low contents of Al and Co, the microstructure remains amorphous throughout the deposition process with a high roughness while at high Al content the microstructure is always crystalline.

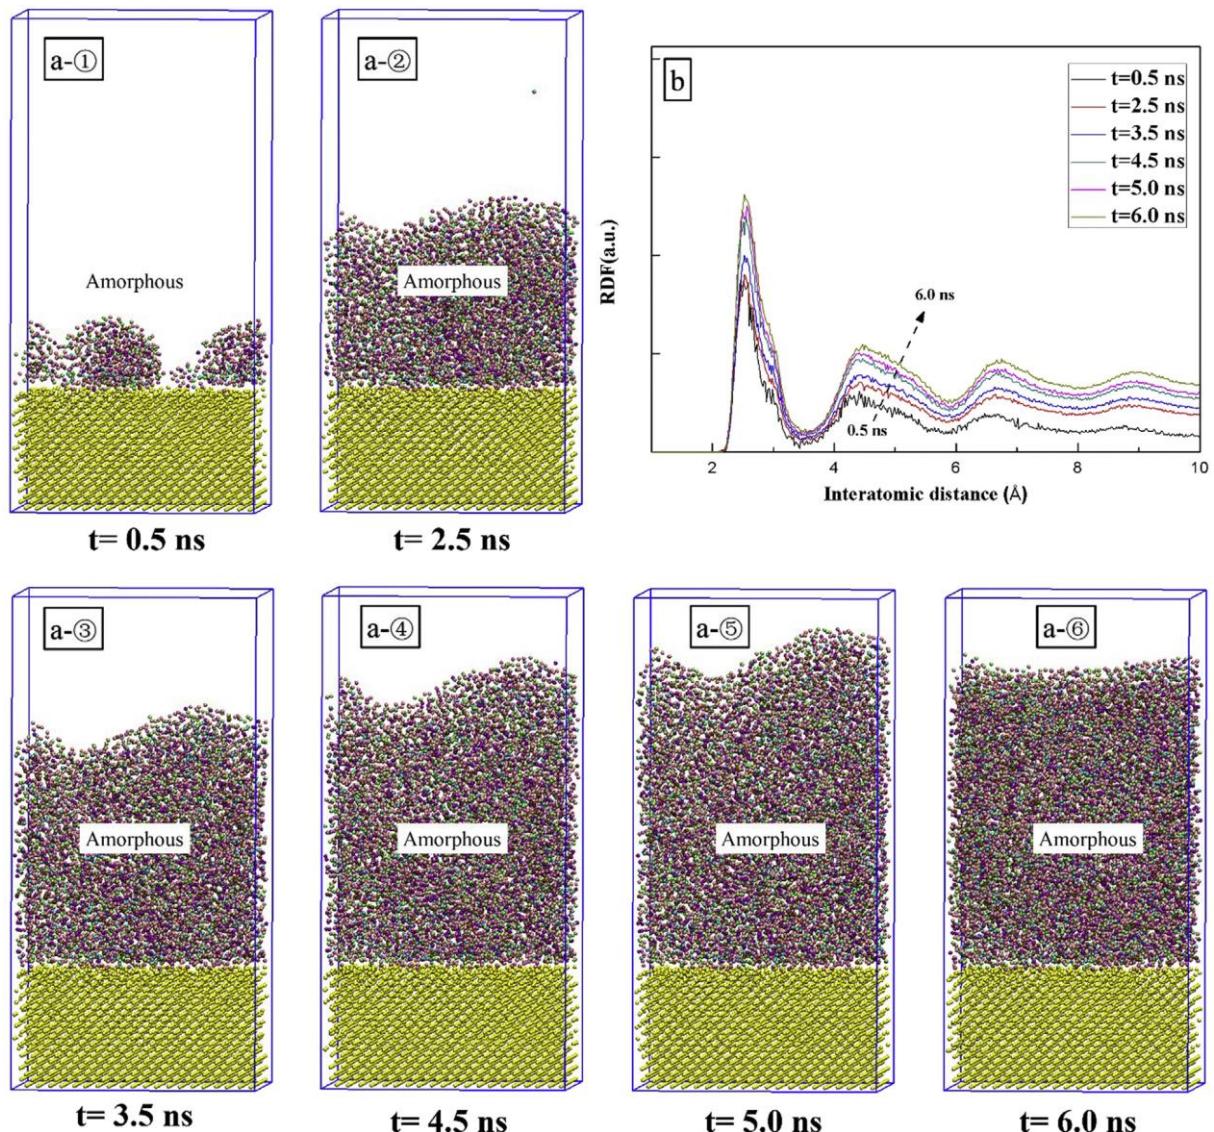

**Figure 28.** Snapshots and RDF of  $\text{Al}_2\text{Co}_9\text{Cr}_{32}\text{Cu}_{39}\text{Fe}_{12}\text{Ni}_6$  deposited on Si (100) substrate at different times  $t$ . ●Al, ●Co, ●Cr, ●Cu, ●Fe, ●Ni, ●Si. Reprinted from Ref. 295

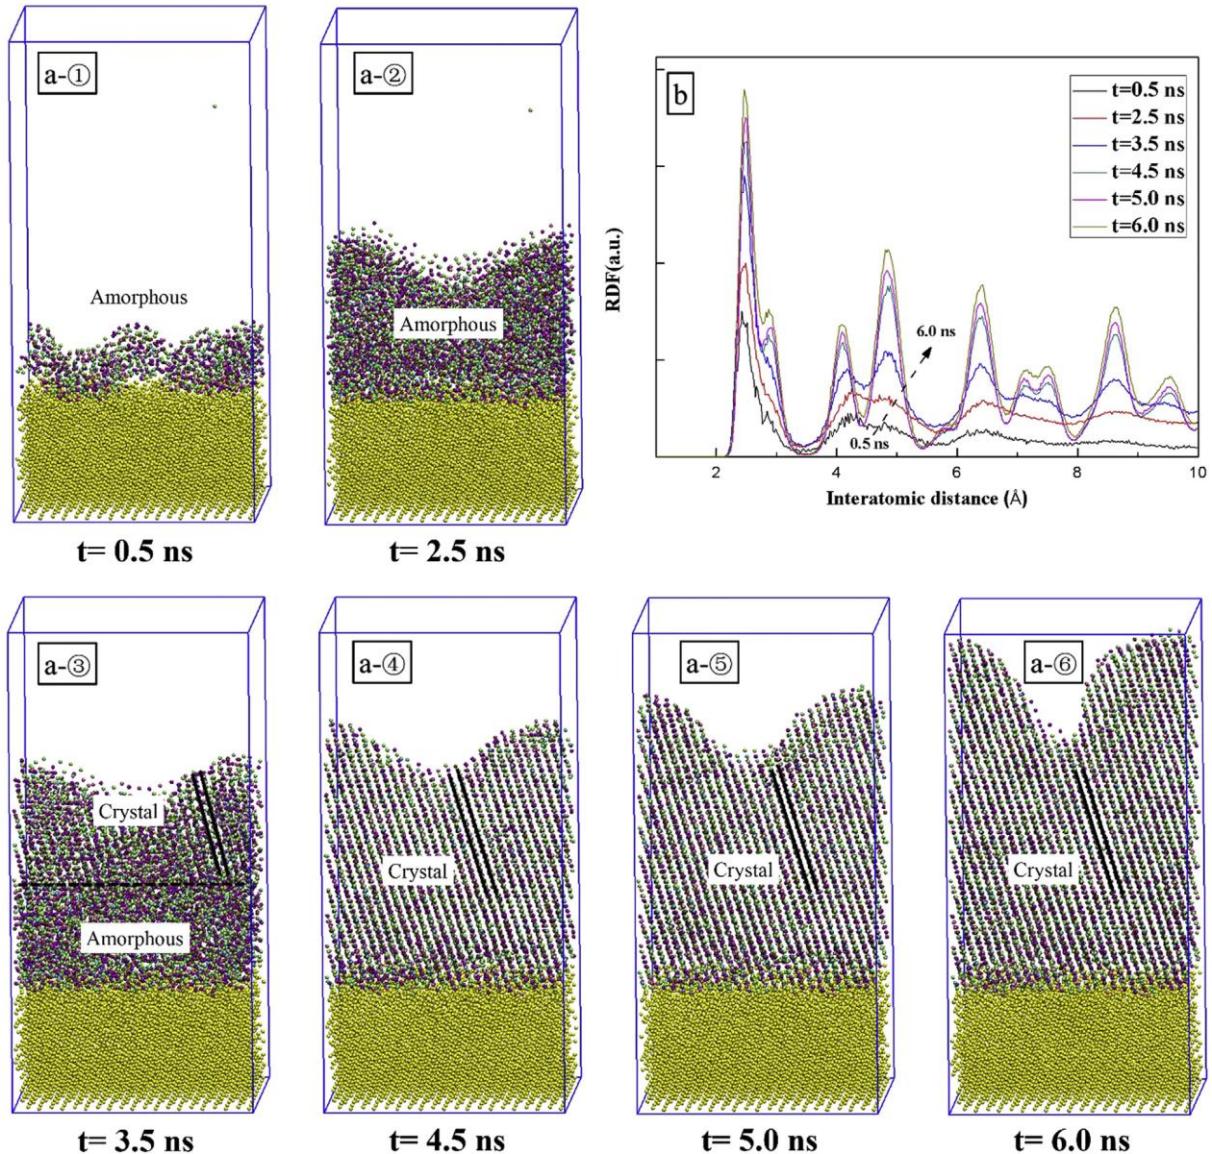

**Figure 29.** Snapshots and RDF of  $\text{Al}_3\text{Co}_{26}\text{Cr}_{15}\text{Cu}_{18}\text{Fe}_{20}\text{Ni}_{18}$  deposited on Si(100) substrate at different times. ●Al, ●Co, ●Cr, ●Cu, ●Fe, ●Ni, ●Si. Reprinted from Ref. 295

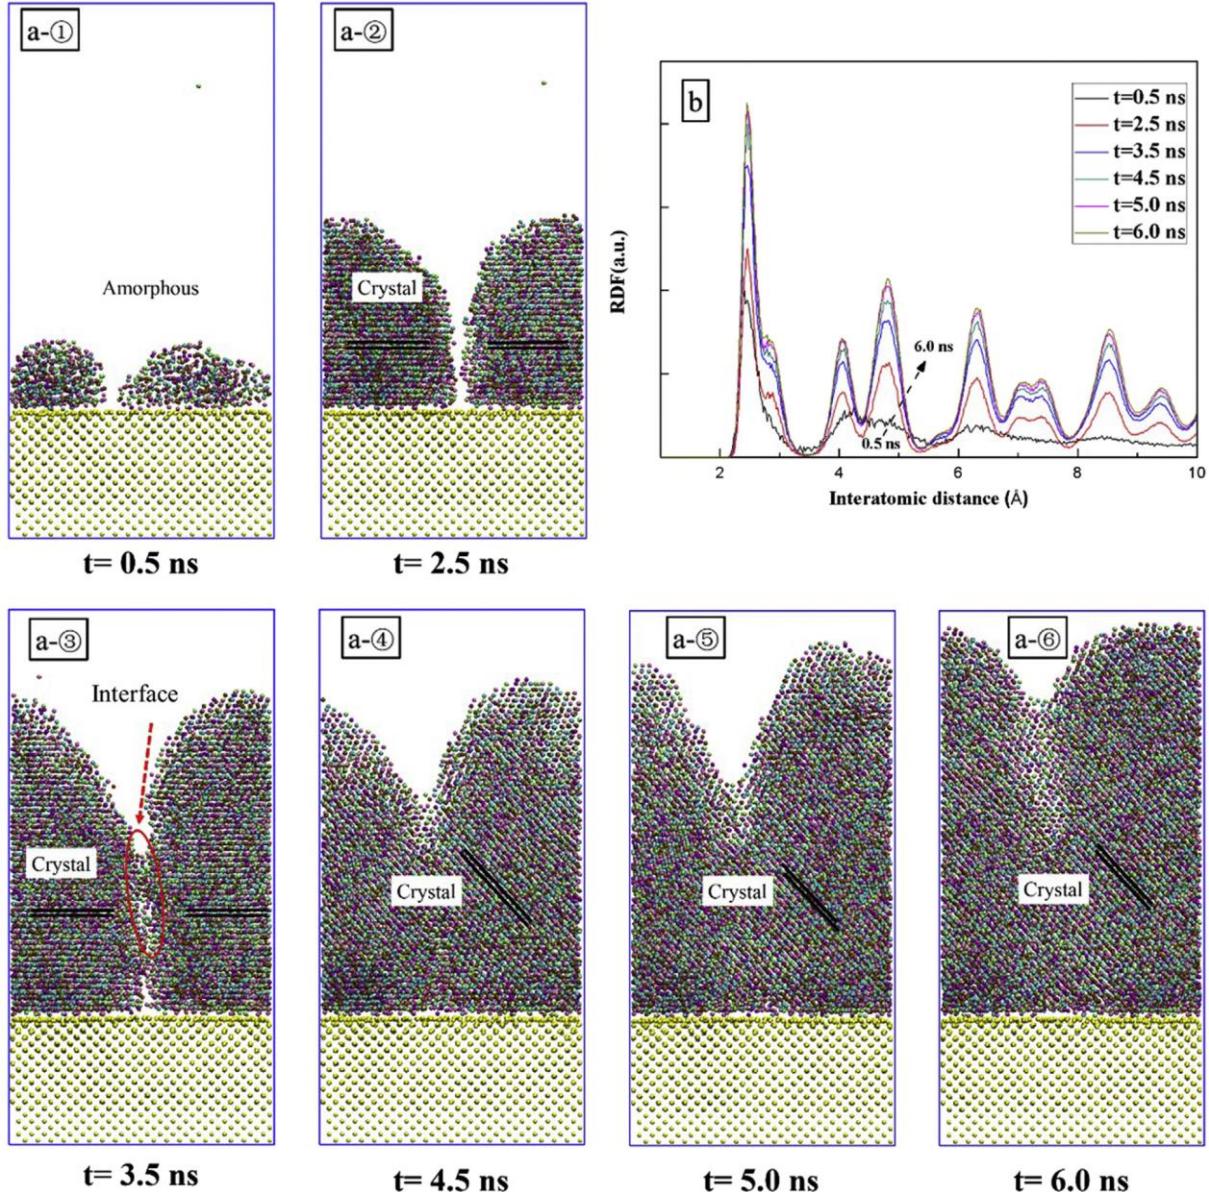

**Figure 30.** Snapshots and RDF of  $\text{Al}_{39}\text{Co}_{10}\text{Cr}_{14}\text{Cu}_{18}\text{Fe}_{13}\text{Ni}_6$  deposited on Si(100) substrate at different times. ●Al, ●Co, ●Cr, ●Cu, ●Fe, ●Ni, ●Si. Reprinted from Ref. 295

MD simulations are thus a very powerful technique for handling thin film deposition calculations and beyond this, the resulting properties. When starting such simulations, care should be taken on several points. The first one is the simulation box size that should be chosen sufficiently large to avoid frequent boundary re-crossing. For systems with low atomic diffusion such as HEAs at moderate temperature,  $10 \times 10 \text{ \AA}^2$  would be enough and would enable the deposition of “thick” films of a few tens of nm. When wishing to address polycrystalline films, large micron size grains are not reachable:  $1 \mu\text{m}^3$  of solid is around  $10^{12}$  atoms, which is far from the possibilities of current computers even with low CPU time cost pair potentials. The second point is the choice of force field.

The faster ones are the pair (2-body) potentials such as Lennard-Jones, Morse, Buckingham and 3-body potentials reducible to sums of 2-body potentials, but their interest is a primary approach and they are not recommended for production runs due to their poor ability to reproduce alloy properties. Many -body potentials such as EAM-MEAM have attracted considerable attention for thin metallic film growth since they are a good compromise between precision of the results and CPU cost. Using reactive force fields such as ReaxFF or COMB3 results in higher costs, but is only relevant for a small number of metal oxide, nitride, carbide and polymer compounds in thin film growth studies. Nevertheless, the CPU cost remains largely below quantum chemistry simulations coupled to MD, often called ab-initio MD or first-principle MD simulations, for such deposition/growth studies. As mentioned previously, building robust interaction potentials with the assistance of AI tools appears to be a promising way.

#### **4.3 . Comparison between MC and MD methods**

Table 1 provides a short comparative list of advantages and disadvantages of Monte-Carlo, kinetic Monte-Carlo, and Molecular dynamics simulations methods for a quick view of benefits in using one of these methods.

**Table 1.** Comparison of MC/kMC and MD methods.

	MC/ kMC Fully stochastic	MD
Statistical nature	Fully stochastic	Fully or partly deterministic
electron collisions	Yes (section 3.). For kMC, yes too, but with increasing computer time	Not for a full plasma description. It comes from the mass difference between electron and atoms that will require extremely small timesteps. A workaround exists with reaxFF forcefield, but the electron mass is fixed to proton mass.
System size dependence	There is no size dependence since only probabilities play a role both in the defining reaction rate and in calculating the associated time. It can treat different time scales	There is a size dependence . The reachable system size is dependent on the force evaluation. This limitation can be overcome using relevant periodic boundary conditions. Confidence in the

	simultaneously, when allowed by the fully stochastic nature of the processes involved.	statistical quantities deduced is dependent on the system size.
Reachable time scales	All	Up to millisecond time scale, if acceleration techniques are implemented.
Input parameters	Fully depends on input parameters such as rate coefficients	Depends only on the initial velocity and position conditions and forcefields. Able to calculate input parameters for MC/kMC simulations.
Required CPU time	Depending on the system complexity, it is not CPU time consuming	Depends on the force field, from CPU time consuming to very time consuming
Capability of addressing complex system	Depends on available data. Quantum chemistry (DFT) or MD simulations can provide missing data	Depends on available forcefields. Missing forcefields can be parametrized using quantum chemistry and machine learning methods.

## 5. Conclusion

This review spans almost all the ways of addressing sputtering, transport and subsequent film growth processes and some film properties. It presents the main features of the simulation methods investigated, coupled to some illustrative examples showing the interest of the method.

The theoretical analytical formula of sputtering and transport provides a first step for building an understanding of the processes involved.

Monte-Carlo models of plasma and transport are easy to handle with a reactor scale implementation capability. This is a major interest of MC methods. The cost is the knowledge of external parameters such as rate constants, which should be of high quality in order to ensure successful comparison with experiments and further, a good predictability capability. Regarding film growth, kMC methods are certainly the most powerful methods for handling growth phenomena up to micron scale grain sizes. Nevertheless, they are dependent on the set of input parameters that should be used. MD simulations, both for sputtering and film growth, can provide insight into all basic phenomena, including tribology, up to billion atom systems. Nevertheless, the robustness of the results largely depends on the quality of the force fields. When considering a multiscale approach, Molecular dynamics can be a source of relevant data for MC, kMC and fluid (continuum) models.

Even if large sizes are not always required, multicore computers with parallel computing software are often required to handle meaningful simulations.

The abundant landscape of simulation approaches and tools provides relevant ways for finding a solution to each problem, provided the problem to be solved is clearly stated and modelled.

### **Acknowledgements**

This work was supported by SAFRAN Tech - Université d'Orléans – CNRS grant #LS 245305 and Conseil Regional du Centre – Val de Loire under Grant MATEX-202100145829.

Elizabeth Rowley-Jolivet is gratefully acknowledged for English language editing.

**Author contributions** PB wrote all drafts of the review article. All authors have read, discussed corrected, and edited all aspects of the review and have approved the final manuscript.

**Data Availability Statement** This manuscript has no associated data or the data will not be deposited. [Authors' comment: The paper is a review article and we have not generated any data.].

**Conflict of interest** The authors declare no competing interests.

## References

- [1] L. Xie, PhD thesis, <https://tel.archives-ouvertes.fr/tel-00933201/document>
- [2] P. J. Kelly, R. D. Arnett, Vacuum 56, 159 (2000) [https://doi.org/10.1016/S0042-207X\(99\)00189-X](https://doi.org/10.1016/S0042-207X(99)00189-X)
- [3] K Sarakinos, J. Alami, S. Konstantinidis, Surface and Coatings Technology 204, 1661 (2010) <https://doi.org/10.1016/j.surfcoat.2009.11.013>
- [4] D. Depla, S. Mahieu, R. Hull, R. M. Osgood, J. Parisi, J. M. Warlimont (Eds: ), Reactive Sputter Deposition (Springer Berlin Heidelberg, 2008)
- [5] A. Bogaerts, I. Kolev, and G. Buyle, In Reactive Sputter Deposition, ed. By D. Depla and S. Mahieu (Berlin: Springer-Verlag, 2008). p. 61
- [6] A. Anders, Journal of Applied Physics 121, 171101 (2017) <https://doi.org/10.1063/1.4978350>
- [7] C. H. Townes, Phys. Rev. 65, 319 (1944) <https://doi.org/10.1103/PhysRev.65.319>
- [8] D. E. Harrison, Phys. Rev. 102, 1473 (1956) <https://doi.org/10.1103/PhysRev.102.1473>
- [9] E. B. Henschke, Physical Review 106, 737 (1957) <https://doi.org/10.1103/PhysRev.106.737>
- [10] D. T. Goldman, A. Simon, Phys. Rev. 111, 383 (1958) <https://doi.org/10.1103/PhysRev.111.383>
- [11] W. Brandt, R. Laubert, Nuclear Instruments and Methods 47, 201 (1967) [https://doi.org/10.1016/0029-554X\(67\)90431-4](https://doi.org/10.1016/0029-554X(67)90431-4)
- [12] G. Chapman, J. Kelly, Australian Journal of Physics 20, 283 (1967) <https://doi.org/10.1071/PH670283>
- [13] P. D. Davidse, Vacuum 17, 139–145 (1967) [https://doi.org/10.1016/0042-207X\(67\)93142-9](https://doi.org/10.1016/0042-207X(67)93142-9)
- [14] M. W. Thompson, 377–414 (1968) <https://doi.org/10.1080/14786436808227358>
- [15] P. Sigmund, Physical review 184, 383 (1969) <https://doi.org/10.1103/PhysRev.184.383>
- [16] P. Sigmund, Rev. Roum. Phys. 17, 969 (1972)
- [17] K. Kanaya, K. Hojou, K. Koga, K. Toki, Japanese Journal of Applied Physics 12, 1297 (1973). <https://doi.org/10.1143/JJAP.12.1297>
- [18] H. Oechsner, Applied Physics 8, 185–198 (1975) <https://doi.org/10.1007/BF00896610>
- [19] H. F. Winters, Advances in Chemistry 158, 1 (1976). <https://doi.org/10.1021/ba-1976-0158.ch001>
- [20] R. Kelly, Radiation Effects 32, 91 (1977) <https://doi.org/10.1080/00337577708237462>
- [21] G. Betz, Surface Science 92, 283 (1980) [https://doi.org/10.1016/0039-6028\(80\)90258-7](https://doi.org/10.1016/0039-6028(80)90258-7)
- [22] P. Sigmund, Journal of Vacuum Science and Technology 17, 396 (1980) <https://doi.org/10.1116/1.570399>
- [23] N. Matsunami, Y. Yamamura, Y. Itikawa, N. Itoh, Y. Kazumata, S. Miyagawa, K. Morita, R. Shimizu, Radiation Effects, 57, 15 (1981) <https://doi.org/10.1080/01422448008218676>
- [24] P. Sigmund, A. Oliva, G. Falcone, Nuclear Instruments and Methods in Physics Research 194, 541 (1982) [https://doi.org/10.1016/0029-554X\(82\)90578-X](https://doi.org/10.1016/0029-554X(82)90578-X)

- [25] Z. Sroubek, Nuclear Instruments and Methods in Physics Research 194, 533 (1982)  
[https://doi.org/10.1016/0029-554X\(82\)90577-8](https://doi.org/10.1016/0029-554X(82)90577-8)
- [26] Y. Yamamura, , N. Matsunami, & N. Itoh, Radiation Effects 68, 83 (1982)  
<https://doi.org/10.1080/01422448208226913>
- [27] N. D. Lang, J. K. Nørskov, Physica Scripta T6, 15 (1983) <https://doi.org/10.1088/0031-8949/1983/T6/002>
- [28] R. Kelly, D. E. Harrison, Materials Science and Engineering 69, 449 (1985)  
[https://doi.org/10.1016/0025-5416\(85\)90346-5](https://doi.org/10.1016/0025-5416(85)90346-5)
- [29] J. B. Malherbe, S. Hofmann, J. M. Sanz, Applied Surface Science 27, 355–365 (1986)  
[https://doi.org/10.1016/0169-4332\(86\)90139-X](https://doi.org/10.1016/0169-4332(86)90139-X)
- [30] G. Falcone, F. Gullo, Physics Letters A 125, 432–434 (1987) [https://doi.org/10.1016/0375-9601\(87\)90178-2](https://doi.org/10.1016/0375-9601(87)90178-2)
- [31] G. Falcone, Surface Science 187, 212 (1987) [https://doi.org/10.1016/S0039-6028\(87\)80133-4](https://doi.org/10.1016/S0039-6028(87)80133-4)
- [32] P. Sigmund, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 27, 1 (1987) [https://doi.org/10.1016/0168-583X\(87\)90004-8](https://doi.org/10.1016/0168-583X(87)90004-8)
- [33] G. Falcone, Sputtering transport theory: The mean energy. Physical Review B 38, 6398–6401 (1988) <https://doi.org/10.1103/PhysRevB.38.6398>
- [34] P. C. Zalm, Surface and Interface Analysis 11, 1 (1988) <https://doi.org/10.1002/sia.740110102>
- [35] M. H Shapiro, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 42, 290–292 (1989) [https://doi.org/10.1016/0168-583X\(89\)90722-2](https://doi.org/10.1016/0168-583X(89)90722-2)
- [36] G. Falcone, La Rivista del Nuovo Cimento della Societa Italiana di Fisica 13, 1 (1990).
- [37] R. S. Mason, M. PichilingiJ. Phys. D: Appl. Phys. 27, 2363 (1994) <https://doi.org/10.1088/0022-3727/27/11/017>
- [38] Z. L. Zhang, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 149, 272–284 (1999) [https://doi.org/10.1016/S0168-583X\(98\)00634-X](https://doi.org/10.1016/S0168-583X(98)00634-X)
- [39] M. Stepanova, & S. K. Dew, Journal of Vacuum Science & Technology A 19, 2805–2816 (2001) <https://doi.org/10.1116/1.1405515>
- [40] M. Stepanova, & S. K. Dew, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 215, 357–365 (2004)  
<https://doi.org/10.1016/j.nimb.2003.09.013>
- [41] G. K. Wehner, & D. Rosenberg, Journal of Applied Physics (2004)  
<https://doi.org/10.1063/1.1735395>
- [42] G. N. V. Wyk, A. H. Lategan, Radiation Effects (2006)  
<https://doi.org/10.1080/01422448208226917>

- [43] R. Behrisch, W. Eckstein, Sputtering by Particle Bombardment: Experiments and Computer Calculations from Threshold to MeV Energies. (Springer Science & Business Media, 2007).
- [44] W. R. Grove, Philosophical Transactions of the Royal Society of London 142, 87–101 (1852)  
<https://doi.org/10.1098/rstl.1852.0008>
- [45] Y. Yamamura, H. Tawara, Atomic Data and Nuclear Data Tables 62, 149–253 (1996)  
<https://doi.org/10.1006/adnd.1996.0005>
- [46] T. Ono, T. Kenmotsu, and T. Muramoto, In Reactive Sputter Deposition, ed. By D. Depla and S. Mahieu (Berlin: Springer-Verlag, 2008). p. 1
- [47] J. F. Ziegler, J. P. Biersack, and U. Littmark, The Stopping and Range of Ions in Solids. (New York: Pergamon Press, 1985)
- [48] J. Lindhard, and M. Scharff, Phys. Rev. 124, 128 (1961)  
<https://doi.org/10.1103/PhysRev.124.128>
- [49] T. Mousel, W. Eckstein, and H. Gnaser, Nucl. Instrum. Methods Phys. Res. B 152 (1999) 36-48  
[https://doi.org/10.1016/S0168-583X\(98\)00976-8](https://doi.org/10.1016/S0168-583X(98)00976-8)
- [50] Y. Yamamura, T. Takiguchi and M. Ishida, Radiat. Eff. Defects Solids 118 (1991) 237-261  
[https://doi.org/10.1016/S0168-583X\(98\)00976-8](https://doi.org/10.1016/S0168-583X(98)00976-8)
- [51] K. Meyer, I. K. Schuller, C. M. Falco , J. Appl. Phys. 52 (1981) 5803–5805  
<https://doi.org/10.1063/1.329473>
- [52] A. Gras-Marti and J. A. Valles-Abarca, J. Appl. Phys. 54 (1983) 1071– 1075  
<https://doi.org/10.1063/1.332113>
- [53] P. Brault, E. Neyts, Catalysis Today 256 (2015) 3–12  
<https://doi.org/10.1016/j.cattod.2015.02.004>
- [54] T. Kenmotsu, Y. Yamamura, T. Ono, T. Kawamura, Journal of Plasma and Fusion Research 80, 406 (2004) <https://doi.org/10.1585/jspf.80.406>
- [55] S. Berg, T. Nyberg, H.-O. Blom, C. Nender, Handbook of Thin Film Process, Technology (Institute of Physics Publishing, Bristol, UK, 1998)
- [56] S. Berg, T. Nyberg, Thin Solid Films 476, 215 (2005) <https://doi.org/10.1016/j.tsf.2004.10.051>
- [57] S. Berg, H.-O. Blom, T. Larsson, C. Nender, J. Vac. Sci Technol. A 5, 202 (1987)  
<https://doi.org/10.1116/1.574104>
- [58] S. Berg, T. Larsson, C. Nender, H.-O. Blom, J. Appl. Phys. 63, 887 (1988)  
<https://doi.org/10.1063/1.340030>
- [59] H. Bartzsch, P. Frach, Surf. Coat. Technol. 142–144, 192 (2001) [https://doi.org/10.1016/S0257-8972\(01\)01087-8](https://doi.org/10.1016/S0257-8972(01)01087-8)

- [60] V.A. Koss, and J.L. Vossen, *J. Vac. Sci. Technol. A: Vac. Surf. Films* 8, 3791 (1990)  
<https://doi.org/10.1116/1.576495>
- [61] H. Ofner, R. Zarwasch, E. Rille, H.K. Pulker, *J. Vac. Sci. Technol. A: Vac. Surf. Films* 9, 2795 (1991)  
<https://doi.org/10.1116/1.577202>
- [62] H. Sekiguchi, T. Murakami, A. Kanzawa, T. Imai, T. Honda, *J. Vac. Sci. Technol. A: Vac. Surf. Films* 14, 2231 (1996) <https://doi.org/10.1116/1.580051>
- [63] S. Berg, T. Nyberg, and T. Kubart, In *Reactive Sputter Deposition*, ed. By D. Depla and S. Mahieu (Berlin: Springer-Verlag, 2008) p. 131
- [64] C. Costin, T. M. Minea, G. Popa, G. Gousset, *Plasma Processes and Polymers* 4, S960 (2007)  
<https://doi.org/10.1002/ppap.200732307>
- [65] S. Kadlec, *Surface and Coatings Technology* 202, 895 (2007)  
<https://doi.org/10.1016/j.surfcoat.2007.06.043>
- [66] I. Kolev, A. Bogaerts, *Journal of Vacuum Science & Technology A* 27, 20 (2008)  
<https://doi.org/10.1116/1.3013856>
- [67] A. Bogaerts, E. Bultinck, I. Kolev, L. Schwaederlé, K. Van Aeken, G. Buyle and D. Depla, *Journal of Physics D: Applied Physics* 42, 194018 (2009) <https://doi.org/10.1088/0022-3727/42/19/194018>
- [68] B. Zheng, Y. Fu, K. Wang, T. Tran, T. Schuelke, Q. H. Fan, *Physics of Plasmas* 28, 014504 (2021)  
<https://doi.org/10.1063/5.0029353>
- [69] C. H. Shon, J. K. Lee, *Applied Surface Science* 192, 258 (2002) [https://doi.org/10.1016/S0169-4332\(02\)00030-2](https://doi.org/10.1016/S0169-4332(02)00030-2)
- [70] A. Bogaerts, M. van Straaten, R. Gijbels, *Journal of Applied Physics* 77, 1868 (1995)  
<https://doi.org/10.1063/1.358887>
- [71] A. Bogaerts, R. Gijbels, R. J. Carman, *Spectrochimica Acta Part B: Atomic Spectroscopy* 53, 1679 (1998) [https://doi.org/10.1016/S0584-8547\(98\)00201-8](https://doi.org/10.1016/S0584-8547(98)00201-8)
- [72] T. M. Minea, J. Bretagne, G. Gousset, *IEEE Transactions on Plasma Science* 27, 94 (1999)  
<https://doi.org/10.1109/27.763060>
- [73] E. Shidoji, N. Nakano, T. Makabe, *Thin Solid Films* 351, 37 (1999) [https://doi.org/10.1016/S0040-6090\(99\)00151-0](https://doi.org/10.1016/S0040-6090(99)00151-0)
- [74] J. Bretagne, C. Boisse Laporte, G. Gousset, O. Leroy, T. M. Minea, D. Pagnon, L. de Poucques, M. Touzeau, *Plasma Sources Sci. Technol.* 12, S33 (2003) <https://doi.org/10.1088/0963-0252/12/4/318>
- [75] C. Costin, L. Marques, G. Popa, G. Gousset, *Plasma Sources Sci. Technol.* 14, 168 (2005)  
<https://doi.org/10.1088/0963-0252/14/1/018>
- [76] T. Yagisawa T. Makabe, *Journal of Vacuum Science & Technology A* 24, 908 (2006)  
<https://doi.org/10.1116/1.2198866>

- [77] I.Kolev, A. Bogaerts, Journal of Applied Physics 104, 093301 (2008)  
<https://doi.org/10.1063/1.2970166>
- [78] E. Bultinck, A. Bogaerts, New J. Phys. 11, 103010 (2009) <https://doi.org/10.1088/1367-2630/11/10/103010>
- [79] E. Bultinck, S. Mahieu, D. Depla, A. Bogaerts, New J. Phys. 11, 023039 (2009)  
<https://doi.org/10.1088/1367-2630/11/2/023039>
- [80] C. Costin, T. M. Minea, G. Popa, G. Gousset, Journal of Vacuum Science & Technology A 28, 322 (2010) <https://doi.org/10.1116/1.3332583>
- [81] E. Bultinck, A. Bogaerts, Plasma Sources Science and Technology 20, 045013 (2011)  
<https://doi.org/10.1088/0963-0252/20/4/045013>
- [82] G. Kawamura, Y. Tomita, A. Kirschner, Journal of Nuclear Materials 415, S192 (2011)  
<https://doi.org/10.1016/j.jnucmat.2010.09.057>
- [83] T. Kozák, A. Dagmar Pajdarová, Journal of Applied Physics 110, 103303 (2011)  
<https://doi.org/10.1063/1.3656446>
- [84] A. Pflug, M. Siemers, C. Schwanke, B. Febty Kurnia,V. Sittinger, B. Szyszka, Materials Technology 26, 10 (2011) <https://doi.org/10.1179/175355511X12941605982028>
- [85] M. A. Raadu, I. Axnäs, J. T. Gudmundsson, C. Huo, N. Brenning, Plasma Sources Sci. Technol. 20, 065007 (2011) <https://doi.org/10.1088/0963-0252/20/6/065007>
- [86] D. Depla, & W. P. Leroy, Thin Solid Films 520, 6337 (2012)  
<https://doi.org/10.1016/j.tsf.2012.06.032>
- [87] F. J. Jimenez, S. K. Dew, Journal of Vacuum Science & Technology A 30, 041302 (2012)  
<https://doi.org/10.1116/1.4712534>
- [88] F. Boydens, W. P.Leroy, R. Persoons, D. Depla, Thin Solid Films 531, 32 (2013)  
<https://doi.org/10.1016/j.tsf.2012.11.097>
- [89] N. Brenning, D. Lundin, T. Minea, C. Costin, C Vitelaru, J. Phys. D: Appl. Phys. 46, 084005 (2013)  
<https://doi.org/10.1088/0022-3727/46/8/084005>
- [90] D. Depla, K. Strijckmans, R. De Gryse, Surface and Coatings Technology 258, 1011 (2014)  
<https://doi.org/10.1016/j.surfcoat.2014.07.038>
- [91] F. J. Jimenez, S. K. Dew, D. J. Field, Journal of Vacuum Science & Technology A 32, 061301 (2014)  
<https://doi.org/10.1116/1.4894270>
- [92] T. M. Minea, C. Costin, A. Revel, D. Lundin, L. Caillault, Surface and Coatings Technology 255, 52–61 (2014) <https://doi.org/10.1016/j.surfcoat.2013.11.050>
- [93] K. Strijckmans, D. Depla, J. Phys. D: Appl. Phys. 47, 235302 (2014). <https://doi.org/10.1088/0022-3727/47/23/235302>

- [94] J. T. Gudmundsson, D. Lundin, G. D. Stancu, N. Brenning, T. M. Minea, Physics of Plasmas 22, 113508 (2015) <https://doi.org/10.1063/1.4935402>
- [95] K. Strijckmans, D. Depla, Applied Surface Science 331, 185–192 (2015)  
<https://doi.org/10.1016/j.apsusc.2015.01.058>
- [96] J. T. Gudmundsson, D. Lundin, N. Brenning, M. A. Raadu, C. Huo and T. M. Minea, Plasma Sources Sci. Technol. 25, 065004 (2016) <https://doi.org/10.1088/0963-0252/25/6/065004>
- [97] A. Revel, T. Minea, S. Tsikata, Physics of Plasmas 23, 100701 (2016)  
<https://doi.org/10.1063/1.4964480>
- [98] N. Brenning, J. T. Gudmundsson, M. A. Raadu, T. J. Petty, T. Minea, D. Lundin, Plasma Sources Sci. Technol. 26, 125003 (2017) <https://doi.org/10.1088/1361-6595/aa959b>
- [99] C. Huo, D. Lundin, J. T. Gudmundsson, M. A. Raadu, J. W. Bradley, N. Brenning J. Phys. D: Appl. Phys. 50, 354003 (2017) <https://doi.org/10.1088/1361-6463/aa7d35>
- [100] D. Lundin, J. T. Gudmundsson, N. Brenning, M. A. Raadu, T. Minea, Journal of Applied Physics 121, 171917 (2017) <https://doi.org/10.1063/1.4977817>
- [101] F. Moens, S. Konstantinidis, D. Depla, Front. Phys. 5, 51 (2017)  
<https://doi.org/10.3389/fphy.2017.00051>
- [102] K. Strijckmans, F. Moens, D. Depla, Journal of Applied Physics 121, 080901 (2017)  
<https://doi.org/10.1063/1.4976717>
- [103] J. Held, A. Hecimovic, A. von Keudell, V. S. von der Gathen, Plasma Sources Sci. Technol. 27, 105012 (2018) <https://doi.org/10.1088/1361-6595/aae236>
- [104] T. Kozák, J. Lazar, Plasma Sources Sci. Technol. 27, 115012 (2018)  
<https://doi.org/10.1088/1361-6595/aaebdd>
- [105] A. Revel, T. Minea, C. Costin, Plasma Sources Sci. Technol. 27, 105009 (2018)  
<https://doi.org/10.1088/1361-6595/aadebe>
- [106] S. Cui, , Z. Wu, H. Lin, S. Xiao, B. Zheng, L. Liu, X. An, R. K. Y. Fu, X. Tian, W. Tan, P. K. Chu, Journal of Applied Physics 125, 063302 (2019) <https://doi.org/10.1063/1.5048554>
- [107] D. Lundin, T. Minea, J. T. Gudmundsson, High Power Impulse Magnetron Sputtering: Fundamentals, Technologies, Challenges and Applications. (Elsevier, 2019).
- [108] B. Zheng, Z. Wu, S. Cui, S. Xiao; L. Liu, H. Lin, R. K. Y. Fu, X. Tian, F. Pan; P. K. Chu, IEEE Transactions on Plasma Science 47, 193 (2019) <https://doi.org/10.1109/TPS.2018.2884475>
- [109] T. Minea, T. Kozák, C. Costin, J. T. Gudmundsson, D. Lundin, in High Power Impulse Magnetron Sputtering, ed. By D. Lundin, T. Minea, J. T. Gudmundsson, (Amsterdam, Elsevier, 2020) p. 159
- [110] H. Eliasson, M. Rudolph, N. Brenning, H. Hajihoseini, M. Zanáška, M. J. Adriaans, M. A. Raadu, T. M. Minea, Plasma Sources Sci. Technol. 30, 115017 (2021) <https://doi.org/10.1088/1361-6595/ac352c>

- [111] M. Rudolph, H. Hajihoseini, M. A. Raadu, J. T. Gudmundsson, N. Brenning, T. M. Minea, A. Anders, D. Lundin, Journal of Applied Physics 129, 033303 (2021) <https://doi.org/10.1063/5.0036902>
- [112] M. Rudolph, H. Hajihoseini, M. A. Raadu, J. T. Gudmundsson, N. Brenning, T. M. Minea, A. Anders, D. Lundin. Plasma Sources Sci. Technol. 30, 045011 (2021)  
<https://doi.org/10.1063/5.0036902>
- [113] T.E. Sheridan, M.J. Goeckner, J. Goree, J. Vac. Sci. Technol. A 8, 30 (1990)  
<https://doi.org/10.1116/1.577093>
- [114] T.E. Sheridan, M.J. Goeckner, J. Goree, J. Vac. Sci. Technol. A 8, 1623 (1990)  
<https://doi.org/10.1116/1.576776>
- [115] J.E. Miranda, M.J. Goeckner, J. Goree, T.E. Sheridan, J. Vac. Sci. Technol. A 8, 1627 (1990)  
<https://doi.org/10.1116/1.576777>
- [116] M.J. Goeckner, J. Goree, T.E. Sheridan, IEEE Trans. Plasma Sci. 19, 301 (1991)  
<https://doi.org/10.1109/27.106828>
- [117] J. Goree, T.E. Sheridan, Appl. Phys. Lett. 59, 1052 (1991) <https://doi.org/10.1063/1.106342>
- [118] J. Li, Q. Chen, Z. Li, J. Phys. D: Appl. Phys. 28, 681 (1995) <https://doi.org/10.1088/0022-3727/28/4/010>
- [119] J. Li, Q. Chen, Z. Li, J. Phys. D: Appl. Phys. 28, 1121 (1995) <https://doi.org/10.1088/0022-3727/28/6/014>
- [120] J. Li, Q. Chen, W. Zhang, Z. Li, J.J. Pan, J. Phys. D: Appl. Phys. 29, 1624 (1996)  
<https://doi.org/10.1088/0022-3727/29/6/031>
- [121] C. Heise, K. Lemke, M. Kock, Contrib. Plasma Phys. 37, 431 (1997)  
<https://doi.org/10.1002/ctpp.2150370505>
- [122] Q.H. Fan, J.J. Gracio, L.Q. Zhou, J. Appl. Phys. 95, 6017 (2004)  
<https://doi.org/10.1063/1.1715133>
- [123] S. Ido, K. Nakamura, Jpn. J. Appl. Phys. 32, 5698 (1993) <https://doi.org/10.1143/JJAP.32.5698>
- [124] S. Ido, K. Nakamura, Vacuum 47, 1035 (1996) [https://doi.org/10.1016/0042-207X\(96\)00119-4](https://doi.org/10.1016/0042-207X(96)00119-4)
- [125] S. Ido, K. Nakamura, Jpn. J. Appl. Phys. 35(Part 1), 2302 (1996)  
<https://doi.org/10.1143/JJAP.35.2302>
- [126] M. Kashiwagi, S. Ido, Vacuum 53, 33 (1999) [https://doi.org/10.1016/S0042-207X\(98\)00417-5](https://doi.org/10.1016/S0042-207X(98)00417-5)
- [127] S. Ido, M. Kashiwagi, M. Takahashi, Jpn. J. Appl. Phys. 38(Part 1), 4450 (1999)  
<https://doi.org/10.1143/JJAP.38.4450>
- [128] S. Ido, T. Suzuki, M. Kashiwagi, Jpn. J. Appl. Phys. 37(Part 1), 965 (1998)  
<https://doi.org/10.1143/JJAP.37.965>
- [129] E. Shidoji, M. Nemoto, T. Nomura, Y. Yoshikawa, Jpn. J. Appl. Phys. 33, 4281 (1994)  
<https://doi.org/10.1143/JJAP.33.4281>

- [130] E. Shidoji, M. Nemoto, T. Nomura, J. Vac. Sci. Technol. A 18, 2858 (2000)  
<https://doi.org/10.1116/1.1312376>
- [131] A. Lopp, C. Braatz, M. Geisler, H. Claus, and J. Trube, 45th Annual Technical Conference Proceedings of the Society of Vacuum Coaters, 170, (2002) , ISSN 0737-5921
- [132] Q.H. Fan, L.Q. Zhou, J.J. Gracio, J. Phys. D: Appl. Phys, 36, 244 (2003)  
<https://doi.org/10.1088/0022-3727/36/3/305>
- [133] T. Kubart, R. Novak, J. Valter, Czech. J. Phys. 54 (Suppl. C), 1027 (2004)
- [134] G. Buyle, D. Depla, J. Haemers, W. De Bosscher, R. De Gryse, in SVC 48<sup>th</sup> Annual Technical Conference Proceedings (Denver, Colorado, 2005)
- [135] E. W. McDaniel, Collision Phenomena in Ionized Gases (Wiley, New York, 1964).
- [136] S. N. Nahar and J.M. Wadehra, Phys. Rev. A 35, 2051 (1987)  
<https://doi.org/10.1103/PhysRevA.35.2051>
- [137] C.K. Birdsall, A.B. Langdon, Plasma Physics via Computer Simulations (Adam Hilger, Bristol, 1991)
- [138] I. Kolev, A. Bogaerts, Plasma Processes Polym. 3, 127 (2006)  
<https://doi.org/10.1002/ppap.200500118>
- [139] G.A. Bird, Molecular gas dynamics and the direct simulation of gas flows, Oxf. Eng. Sci. Ser. (1994).
- [140] M. Turowski, M. Jupé, T. Melzig, P. Moskovkin, A. Daniel, A. Pflug, S. Lucas, D. Ristau, Thin Solid Films 592, 240 (2015) <https://doi.org/10.1016/j.tsf.2015.04.015>
- [141] J. N., Brooks, D. N. Ruzic, Journal of Nuclear Materials 176-177, 278 (1990)  
[https://doi.org/10.1016/0022-3115\(90\)90060-Z](https://doi.org/10.1016/0022-3115(90)90060-Z)
- [142] J. P. Biersack, W. Eckstein, Appl. Phys. A 34, 73 (1984) <https://doi.org/10.1007/BF00614759>
- [143] W. Möller, W. Eckstein, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 2, 814 (1984) [https://doi.org/10.1016/0168-583X\(84\)90321-5](https://doi.org/10.1016/0168-583X(84)90321-5)
- [144] W. Eckstein, J. P. Biersack, Appl. Phys. A 37, 95 (1985) <https://doi.org/10.1007/BF00618859>
- [145] J. P. Biersack, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 27, 21 (1987) [https://doi.org/10.1016/0168-583X\(87\)90005-X](https://doi.org/10.1016/0168-583X(87)90005-X)
- [146] J. P. Biersack, S. Berg, C. Nender, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 59–60, 21 (1991) [https://doi.org/10.1016/0168-583X\(91\)95167-C](https://doi.org/10.1016/0168-583X(91)95167-C)
- [147] I. Strašík, M. Pavlovič, Radiation Effects and Defects in Solids 164, 470–476 (2009)  
<https://doi.org/10.1080/10420150902949910>

- [148] R. E. Stoller, M.B. Toloczko, G.S.Was, A.G.Certain , S.Dwaraknath, F. A. Garner, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 310, 75 (2013) <https://doi.org/10.1016/j.nimb.2013.05.008>
- [149] V. I. Shulga, Applied Surface Science 439, 456–461 (2018)  
<https://doi.org/10.1016/j.apsusc.2018.01.039>
- [150] D. N. Ruzic, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 47, 118–125 (1990) [https://doi.org/10.1016/0168-583X\(90\)90019-Q](https://doi.org/10.1016/0168-583X(90)90019-Q)
- [151] Y. Yamamura, Y. Mizuno, H. Kimura, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 13, 393 (1986) [https://doi.org/10.1016/0168-583X\(86\)90535-5](https://doi.org/10.1016/0168-583X(86)90535-5)
- [152] Y. Yamamura, C. Mössner, H. Oechsner, Radiation Effects 103, 25 (1987)  
<https://doi.org/10.1080/00337578708221239>
- [153] Y. Yasunori, T. Wataru, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 29, 461 (1987) [https://doi.org/10.1016/0168-583X\(87\)90057-7](https://doi.org/10.1016/0168-583X(87)90057-7)
- [154] Y. Yamamura, K. Muraoka, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 42, 175 (1989) [https://doi.org/10.1016/0168-583X\(89\)90704-0](https://doi.org/10.1016/0168-583X(89)90704-0)
- [155] Yamamura, Y. & Tawara, Atomic Data and Nuclear Data Tables 62, 149 (1996)  
<https://doi.org/10.1006/adnd.1996.0005>
- [156] Z. Li, T. Kenmotsu, T. Kawamura, T. Ono, Y. Yamamura, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 153, 331 (1999)  
[https://doi.org/10.1016/S0168-583X\(98\)01010-6](https://doi.org/10.1016/S0168-583X(98)01010-6)
- [157] T. Kenmotsu, Y. Yamamura, T. Muramoto, N. Hirotani, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 228, 369 (2005)  
<https://doi.org/10.1016/j.nimb.2004.10.072>
- [158] T. Motohiro, J. Vac. Sci. Technol A 4, 189 (1986) <https://doi.org/10.1116/1.573469>
- [159] Emmerlich, J., Mráz, S., Snyders, R., Jiang, K. & Schneider, Vacuum 82, 867 (2008)  
<https://doi.org/10.1016/j.vacuum.2007.10.011>
- [160] A. Bogaerts, M. van Straaten, R. Gijbels, Journal of Applied Physics 77, 1868 (1995)  
<https://doi.org/10.1063/1.358887>
- [161] Y. Yamamura, M. Ishida, Journal of Vacuum Science & Technology A 13, 101 (1995)  
<https://doi.org/10.1116/1.579874>

- [162] S. Mahieu, G.Buyle, D.Depla, S.Heirwegh, P.Ghekiere, R.De Gryse, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 243, 313 (2006) <https://doi.org/10.1016/j.nimb.2005.09.018>
- [163] V. Abhilash, Balu, R., Balaji, S., Senthil Nathan, S. & Mohan, S Computational Materials Science 30, 523 (2004) <https://doi.org/10.1016/j.commatsci.2004.02.046>
- [164] K. V. Aeken, S. Mahieu, D. Depla, J. Phys. D: Appl. Phys. 41, 205307 (2008) <https://doi.org/10.1088/0022-3727/41/20/205307>
- [165] S. Kadlec, C. Quaeyhaegens, G. Knuyt, L. Stals, Surface and Coatings Technology 97, 633 (1997) [https://doi.org/10.1016/S0257-8972\(97\)00375-7](https://doi.org/10.1016/S0257-8972(97)00375-7)
- [166] K. Macàk, P. Macàk, U. Helmersson, Computer Physics Communications 120, 238 (1999) [https://doi.org/10.1016/S0010-4655\(99\)00245-3](https://doi.org/10.1016/S0010-4655(99)00245-3)
- [167] T. Motohiro, Y. Taga, Thin Solid Films 112, 161 (1984) [https://doi.org/10.1016/0040-6090\(84\)90493-0](https://doi.org/10.1016/0040-6090(84)90493-0)
- [168] A. M. Myers, J. R. Doyle, J. R Abelson, D. N. Ruzic, Journal of Vacuum Science & Technology A 9, 614 (1991) <https://doi.org/10.1116/1.577375>
- [169] A. M. Myers, J. R. Doyle, D. N Ruzic, Journal of Applied Physics 72, 3064 (1992) <https://doi.org/10.1063/1.351464>
- [170] P. K. Petrov, V. A. Volpyas, R. A. Chakalov, Vacuum 52, 427 (1999) [https://doi.org/10.1016/S0042-207X\(98\)00326-1](https://doi.org/10.1016/S0042-207X(98)00326-1)
- [171] G. M. Turner, I. S. Falconer, B. W. James, D. R. McKenzie, Journal of Applied Physics 65, 3671 (1989) <https://doi.org/10.1063/1.342593>
- [172] O. Yamazaki, K. Iyanagi, S. Takagi, K. Nanbu, Jpn. J. Appl. Phys. 41, 1230 (2002) <https://doi.org/10.1143/JJAP.41.1230>
- [173] K. Bobzin, R. P. Brinkmann, T. Mussenbrock, N. Bagcivan, R. H. Brugnara, M. Schäfer, and J. Trieschman, Surface and Coatings Technology 237, 176 (2013) <https://doi.org/10.1016/j.surfcoat.2013.08.018>
- [174] R. Elsing, Surface and Coatings Technology 49, 132 (1991) [https://doi.org/10.1016/0257-8972\(91\)90044-W](https://doi.org/10.1016/0257-8972(91)90044-W)
- [175] T. Heberlein, G. Krautheim, W. Wuttke, Vacuum 42, 47 (1991) [https://doi.org/10.1016/0042-207X\(91\)90076-U](https://doi.org/10.1016/0042-207X(91)90076-U)
- [176] A. P. J. Jansen, An Introduction to Kinetic Monte Carlo Simulations of Surface Reactions. (Springer, 2012).
- [177] S. Lucas and P. Moskovkin, Thin Solid Films 518, 5355 (2010) <https://doi.org/10.1016/j.tsf.2010.04.064>

- [178] N. Cheimarios, D. To, G. Kokkoris, G. Memos, A. G. Boudouvis, *Frontiers in Physics* 9, 631918 (2021) <https://doi.org/10.3389/fphy.2021.631918>
- [179] G. H. Gilmer, H. Huang, C. Roland, *Computational Materials Science* 12, 354 (1998) [https://doi.org/10.1016/S0927-0256\(98\)00022-6](https://doi.org/10.1016/S0927-0256(98)00022-6)
- [180] G. H. Gilmer, H. Huang, T. D de la Rubia, J. Dalla Torre, F. Baumann, *Thin Solid Films* 365, 189 (2000) [https://doi.org/10.1016/S0040-6090\(99\)01057-3](https://doi.org/10.1016/S0040-6090(99)01057-3)
- [181] H. N. G. Wadley, X. Zhou, R. A. Johnson, M. Neurock, *Progress in Materials Science* 46, 329 (2001) [https://doi.org/10.1016/S0079-6425\(00\)00009-8](https://doi.org/10.1016/S0079-6425(00)00009-8)
- [182] Y. Wang, in 31st Computers and Information in Engineering Conference (American Society of Mechanical Engineers Digital Collection, 2012) p; 241 <https://doi.org/10.1115/DETC2011-48570>
- [183] L. A. Zepeda-Ruiz, G. H. Gilmer, in *Handbook of Crystal Growth* (Second Edition) ed By T. Nishinaga, (Elsevier, 2015) p. 445 <https://doi.org/10.1016/B978-0-444-56369-9.00010-1>.
- [184] L. A. Zepeda-Ruiz, G. H. Gilmer, C. C. Walton, A. V. Hamza, E. Chason, *Journal of Crystal Growth* 312, 1183–1187 (2010) <https://doi.org/10.1016/j.jcrysGro.2009.12.035>
- [185] J. Cho, S. G. Terry, R. LeSar, C. G. Levi, *Materials Science and Engineering: A* 391, 390–401 (2005) <https://doi.org/10.1016/j.msea.2004.09.015>
- [186] J. Dalla Torre, G. H. Gilmer, D. L. Windt, R. Kalyanaraman, F. H. Baumann, P. L. O’Sullivan, J. Sapjeta, T. Díaz de la Rubia, M. Djafari Rouhani *Journal of Applied Physics* 94, 263–271 (2003) <https://doi.org/10.1063/1.1579112>
- [187] J. Dervaux, P. A. Cormier, P. Moskovkin, O. Douheret, S. Konstantinidis, R. Lazzaroni, S. Lucas, R. Snyders, *Thin Solid Films* 636, 644–657 (2017). <https://doi.org/10.1016/j.tsf.2017.06.006>
- [188] F. Elsholz, E. Schöll, A. Rosenfeld, *physica status solidi (b)* 244, 3639 (2007) <https://doi.org/10.1002/pssb.200743257>
- [189] V. Godinho, P. Moskovkin, R. Álvarez, J. Caballero-Hernández, R. Schierholz, B. Bera, J. Demarche, A. Palmero, A. Fernández and S. Lucas, *Nanotechnology* 25, 355705 (2014) <https://doi.org/10.1088/0957-4484/25/35/355705>
- [190] L. Jablonka, P. Moskovkin, Z. Zhang, S.-L. Zhang, S Lucas, T. Kubart, *J. Phys. D: Appl. Phys.* 52, 365202 (2019) <https://doi.org/10.1088/1361-6463/ab28e2>
- [191] Z. Liu, L. Yu, K.-I. Yao, X.-b. Jing, X. Li, X.-Z. Sun, *J. Phys. D: Appl. Phys.* 38, 4202 (2005) <https://doi.org/10.1088/0022-3727/38/23/010>
- [192] F. Nita, C. Mastail, G. Abadias, *Phys. Rev. B* 93, 064107 (2016) <https://doi.org/10.1103/PhysRevB.93.064107>
- [193] R. Mareus, C. Mastail, F. An̄ḡay, N. Brunetière, G. Abadias, *Surface and Coatings Technology* 399, 126130 (2020) <https://doi.org/10.1016/j.surfcoat.2020.126130>

- [194] L. Rosenthal, A. Filinov, M. Bonitz, V. Zaporojtchenko, & F. Faupel, Contributions to Plasma Physics 51, 971–980 (2011) <https://doi.org/10.1002/ctpp.201100034>
- [195] R. Tonneau, P Moskovkin, J Muller, T Melzig, E Haye, S Konstantinidis, A Pflug, S Lucas, J. Phys. D: Appl. Phys. 54, 155203 (2021) <https://doi.org/10.1088/1361-6463/abd72a>
- [196] J. Lindhard and M. Scharff, Phys. Rev. 124, 128 (1961)  
<https://doi.org/10.1103/PhysRev.124.128>
- [197] D. Graves and P. Brault, J. Phys. D 42 (2009) 194011 <https://doi.org/10.1088/0022-3727/42/19/194011>
- [198] A. Omelchenko, A. Nakano, K. Tsukura, R. K. Kalia and P. Vashishta, in Advances in Metal and Semiconductors Clusters vol 4 (Greenwich, CT: JAI Press, 1998) p. 263
- [199] M. P. Allen and D. J. Tildesley Computer Simulations of Liquids (New York: Oxford University Press, 1987)
- [200] J. M. Haile, Molecular Dynamics Simulations (New York, Wiley 1992)
- [201] D. C. Rapaport The Art of Molecular Dynamics Simulations (Cambridge: Cambridge University Press 1995)
- [202] D. Frenkel and B. Smit Understanding Molecular Simulation (Orlando, FL: Academic Press 2001)
- [203] E. Neyts, P. Brault, Plasma Processes and Polymers 14 (2017) 1600145  
<https://doi.org/10.1002/ppap.201600145>
- [204] L. Xie, P. Brault, J.-M. Bauchire, A.-L. Thomann, L. Bedra, J. Phys. D: Appl. Phys. 47, 224004 (2014) <https://doi.org/10.1088/0022-3727/47/22/224004>
- [205] A. Wucher, B. J. Garrison, Surface Science 260, 257 (1992) [https://doi.org/10.1016/0039-6028\(92\)90040-D](https://doi.org/10.1016/0039-6028(92)90040-D)
- [206] B. J. Thijssse, T. P. C. Klaver, E. F. C. Haddeman, Applied Surface Science 231–232, 29–38 (2004)  
<https://doi.org/10.1016/j.apsusc.2004.03.207>
- [207] D. E. Harrison, Journal of Applied Physics 52, 1499–1508 (1981)  
<https://doi.org/10.1063/1.329788>
- [208] O. J. Tucker, D. S. Ivanov, L. V. Zhigilei, R. E. Johnson, E. M. Bringa, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 228, 163–169 (2005) <https://doi.org/10.1016/j.nimb.2004.10.040>
- [209] L. Chen, A. Kaiser, M. Probst, S. Shermukhamedov, Nucl. Fusion 61, 016031 (2020)  
<https://doi.org/10.1088/1741-4326/abc9f4>
- [210] G. Betz, R. Kirchner, W. Husinsky, F. Rüdenauer, H. M. Urbassek, Radiation Effects and Defects in Solids null, 251–266 (1994) <https://doi.org/10.1080/10420159408219788>

- [211] Z. Insepov, I. Yamada, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 99, 248–252 (1995) [https://doi.org/10.1016/0168-583X\(95\)00322-3](https://doi.org/10.1016/0168-583X(95)00322-3)
- [212] G. Betz, W. Husinsky, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 102, 281 (1995) [https://doi.org/10.1016/0168-583X\(95\)80155-F](https://doi.org/10.1016/0168-583X(95)80155-F)
- [213] H. Gades, H. M. Urbassek, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 102, 261 (1995) [https://doi.org/10.1016/0168-583X\(95\)80152-C](https://doi.org/10.1016/0168-583X(95)80152-C)
- [214] J. E. Rubio, L. A. Marqués, M. Jaraíz, L. A. Bailón, J. Barbolla, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 102, 301 (1995) [https://doi.org/10.1016/0168-583X\(95\)80157-H](https://doi.org/10.1016/0168-583X(95)80157-H)
- [215] R. E. Johnson, M. Liu, J. Chem. Phys. 104, 6041 (1996) <https://doi.org/10.1063/1.471340>
- [216] L. A. Marqués, J. E. Rubio, M. Jaraíz, L. A. Bailón, J. J. Barbolla, Journal of Applied Physics 81, 1488 (1997) <https://doi.org/10.1063/1.363914>
- [217] H. M. Urbassek, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 122, 427 (1997) [https://doi.org/10.1016/S0168-583X\(96\)00681-7](https://doi.org/10.1016/S0168-583X(96)00681-7)
- [218] N. A. Kubota, D. J. Economou, S. J. Plimpton, Journal of Applied Physics 83, 4055 (1998) <https://doi.org/10.1063/1.367225>
- [219] V. N. Samoilov, A. E. Tatur, N. A. Kovaleva, A. E. Kozhanov, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 153, 319 (1999) [https://doi.org/10.1016/S0168-583X\(99\)00216-5](https://doi.org/10.1016/S0168-583X(99)00216-5)
- [220] E. M. Bringa, R. E. Johnson, M. Jakas, Phys. Rev. B 60, 15107 (1999) <https://doi.org/10.1103/PhysRevB.60.15107>
- [221] E. E Zhurkin, A. S. Kolesnikov, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 193, 822 (2002) [https://doi.org/10.1016/S0168-583X\(02\)00911-4](https://doi.org/10.1016/S0168-583X(02)00911-4)
- [222] A. V. Krasheninnikov, K. Nordlund, E. Salonen, J. Keinonen, C. H. Wu, Computational Materials Science 25, 427 (2002) [https://doi.org/10.1016/S0927-0256\(02\)00318-X](https://doi.org/10.1016/S0927-0256(02)00318-X)
- [223] E. Salonen, K. Nordlund, J. Keinonen, C. H. Wu, Journal of Nuclear Materials 313–316, 404 (2003) [https://doi.org/10.1016/S0022-3115\(02\)01397-1](https://doi.org/10.1016/S0022-3115(02)01397-1)
- [224] M. H. Shapiro, P. Lu, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 215, 326 (2004) <https://doi.org/10.1016/j.nimb.2003.08.036>

- [225] C. Anders, H. M. Urbassek, & R. E. Johnson, Phys. Rev. B 70, 155404 (2004)  
<https://doi.org/10.1103/PhysRevB.70.155404>
- [226] K. O. E Henriksson, K. Nordlund, & J. Keinonen, Phys. Rev. B 71, 014117 (2005)  
<https://doi.org/10.1103/PhysRevB.71.014117>
- [227] E. Despiau-Pujo, P. Chabert, D. B. Graves, Journal of Vacuum Science & Technology A 26, 274 (2008) <https://doi.org/10.1116/1.2836408>
- [228] A. Yu. Nikiforov, High Energy Chem 42, 235 (2008)  
<https://doi.org/10.1134/S0018143908030090>
- [229] B. Weidtmann, A. Duvenbeck, A. Wucher Applied Surface Science 255, 813 (2008)  
<https://doi.org/10.1016/j.apsusc.2008.05.062>
- [230] A. Ito, Y. Wang, S. Irle, K. Morokuma, H. Nakamura, Journal of Nuclear Materials 390–391, 183 (2009) <https://doi.org/10.1016/j.jnucmat.2009.01.163>
- [231] A.-P. Prskalo, S. Schmauder, C. Ziebert, J. Ye, S. Ulrich, Surface and Coatings Technology 204, 2081 (2010) <https://doi.org/10.1016/j.surfcoat.2009.09.043>
- [232] A. Duvenbeck, B. Weidtmann, A. Wucher, J. Phys. Chem. C 114, 5715 (2010)  
<https://doi.org/10.1021/jp905923w>
- [233] O. A. Restrepo, A. Delcorte, J. Phys. Chem. C 115, 12751 (2011)  
<https://doi.org/10.1021/jp201183a>
- [234] A. Duvenbeck, S. Hanke, B. Weidtmann, A. Wucher, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 269, 1661 (2011)  
<https://doi.org/10.1016/j.nimb.2010.11.082>
- [235] C. Yan, Q. Y. Zhang, AIP Advances 2, 032107 (2012) <https://doi.org/10.1063/1.4738951>
- [236] F. Sefta, N. Juslin, K. D. Hammond, B. D. Wirth, Journal of Nuclear Materials 438, S493 (2013)  
<https://doi.org/10.1016/j.jnucmat.2013.01.101>
- [237] V. Cristaudo, C. Poleunis, B. Czerwinski, A. Delcorte, Surface and Interface Analysis 46, 79 (2014) <https://doi.org/10.1002/sia.5424>
- [238] T. Aoki, J Comput Electron 13, 108 (2014) <https://doi.org/10.1007/s10825-013-0504-5>
- [239] M. L. Nietiadi, L. Sandoval, H. M. Urbassek, W. Möller, Phys. Rev. B 90, 045417 (2014)  
<https://doi.org/10.1103/PhysRevB.90.045417>
- [240] L. Pentecoste, P. Brault, A.-L. Thomann, P. Desgardin, T. Lecas, T. Belhabib, M.-F. Barthe, T. Sauvage, J. Nucl. Mat. 470, 44 (2016) <https://doi.org/10.1016/j.jnucmat.2015.12.017>
- [241] P. Brault, S. Chuon, J.-M. Bauchire, Front. Phys. 4, 20 (2016)  
<https://doi.org/10.3389/fphy.2016.00020>
- [242] L. Pentecoste, A.-L. Thomann, P. Brault, T. Lecas, P. Desgardin, T. Sauvage, M.-F. Barthe, Acta Materialia, 141, 47 (2017) <https://doi.org/10.1016/j.actamat.2017.08.065>

- [243] A. Delcorte, K. Moshkunov, M. Debongnie Journal of Vacuum Science & Technology B 36, 03F109 (2018) <https://doi.org/10.1116/1.5012981>
- [244] A. A. Sycheva, E. N. Voronina, T. V. Rakhimova, J. Surf. Investig. 12, 1270 (2018)  
<https://doi.org/10.1134/S1027451019010191>
- [245] J. Jussila, F. Granberg, K. Nordlund, Nuclear Materials and Energy 17, 113–122 (2018)  
<https://doi.org/10.1016/j.nme.2018.08.002>
- [246] A. A. Sycheva, E. N. Voronina, T. V. Rakhimova, A. T. Rakhimov, Applied Surface Science 475, 1021 (2019) <https://doi.org/10.1016/j.apsusc.2019.01.078>
- [247] T. Gergs, T. Mussenbrock, J. A Trieschmann, Journal of Applied Physics 132, 063302 (2022)  
<https://doi.org/10.1063/5.0098040>
- [248] N. Lümmen, T. Kraska, Nanotechnology 15, 525 (2004) <https://doi.org/10.1088/0957-4484/15/5/021>
- [249] N. Lümmen, T. Kraska, Nanotechnology 16, 2870 (2005) <https://doi.org/10.1088/0957-4484/16/12/023>
- [250] N. Lümmen, T. Kraska, Phys. Rev. B 71, 205403 (2005)  
<https://doi.org/10.1103/PhysRevB.71.205403>
- [251] N. Lümmen, T. Kraska, Eur. Phys. J. D 41, 247 (2007) <https://doi.org/10.1140/epjd/e2006-00210-4>
- [252] P. Brault, Frontiers in Physics 6, 59 (2018) <https://doi.org/10.3389/fphy.2018.00059>
- [253] P. Brault, W. Chamorro-Coral, S. Chuon, A. Caillard, J.-M. Bauchire, S. Baranton, C. Coutanceau & E. Neyts, Front. Chem. Sci. Eng. 13, 324 (2019) <https://doi.org/10.1007/s11705-019-1792-5>
- [254] E. Goudeli, 23, 155 (2019) <https://doi.org/10.1016/j.coche.2019.04.001>
- [255] P. Grammatikopoulos, Current Opinion in Chemical Engineering 23, 164 (2019)  
<https://doi.org/10.1016/j.coche.2019.04.004>
- [256] J.-G. Mattei, P. Grammatikopoulos, J. Zhao, V. Singh, J. Vernieres, S. Steinhauer, A. Porkovich, E. Danielson, K. Nordlund, F. Djurabekova, M. Sowwan, Chem. Mater. 31, 2151 (2019)  
<https://doi.org/10.1021/acs.chemmater.9b00129>
- [257] P. Brault, Energies 13, 3584 (2020) <https://doi.org/10.3390/en13143584>
- [258] B.S.R. Kouamé, S. Baranton, P. Brault, C. Canaff, W. Chamorro-Coral, A. Caillard, K. De Oliveira Vigier, C. Coutanceau, Electrochimica Acta 329, 135161 (2020)  
<https://doi.org/10.1016/j.electacta.2019.135161>
- [259] K.-H. Müller, Surface Science 184, L375 (1987) [https://doi.org/10.1016/S0039-6028\(87\)80265-0](https://doi.org/10.1016/S0039-6028(87)80265-0)
- [260] K. H. Müller, Journal of Applied Physics 62, 1796 (1987) <https://doi.org/10.1063/1.339559>
- [261] K-H. Müller, Journal of Vacuum Science & Technology A 6, 1690 (1988)  
<https://doi.org/10.1116/1.575309>

- [262] I. Kwon, R. Biswas, G. S. Grest, C. M. Soukoulis, Phys. Rev. B 41, 3678 (1990)  
<https://doi.org/10.1103/PhysRevB.41.3678>
- [263] C. M. Gilmore, J. A. Sprague, Phys. Rev. B 44, 8950 (1991)  
<https://doi.org/10.1103/PhysRevB.44.8950>
- [264] C. C. Fang, F. Jones, V. Prasad, MRS Online Proceedings Library (OPL) , Volume 280: Symposium B – Evolution of Surface and Thin Film Microstructure, 463 (1992) <https://doi.org/10.1557/PROC-280-463>
- [265] C. C. Fang, V. Prasad, F. Jones, *Journal of Vacuum Science & Technology A* **11**, 2778 (1993)  
<https://doi.org/10.1116/1.578641>
- [266] C. C. Fang, F. Jones, V. Prasad, *Journal of Applied Physics* **74**, 4472 (1993)  
<https://doi.org/10.1063/1.354363>
- [267] C. C. Fang, F. Jones, R. R. Kola, G. K. Celler, V. Prasad, Journal of Vacuum Science & Technology B: Microelectronics and Nanometer Structures Processing, Measurement, and Phenomena 11, 2947 (1993) <https://doi.org/10.1116/1.586566>
- [268] R. W. Smith, F. Ying, & Srolovitz, D. J. MRS Online Proceedings Library 403, 39 (1995)  
<https://doi.org/10.1557/PROC-403-39>
- [269] N. A. Marks, D. R. McKenzie, B. A. Pailthorpe, Phys. Rev. B 53, 4117(1996)  
<https://doi.org/10.1103/PhysRevB.53.4117>
- [270] F. Ying, R. W. Smith, & D. J. Srolovitz, *Appl. Phys. Lett.* **69**, 3007 (1996)  
<https://doi.org/10.1063/1.116821>
- [271] J. D. Kress, D. E. Hanson, A. F. Voter, Journal of Vacuum Science & Technology A **17**, 2819 (1999) <https://doi.org/10.1116/1.581948>
- [272] U. Hansen, S. Rodgers, K. F. Jensen, Phys. Rev. B 62, 2869 (2000)  
<https://doi.org/10.1103/PhysRevB.62.2869>
- [273] S.-P. Ju, C.-I. Weng, J.-G. Chang, C.-C. Hwang, Surface and Coatings Technology 149, 135 (2002)  
[https://doi.org/10.1016/S0257-8972\(01\)01445-1](https://doi.org/10.1016/S0257-8972(01)01445-1)
- [274] Ju, S.-P., Weng, C.-I., Chang, J.-G. & Hwang, C.-C. Journal of Vacuum Science & Technology B: Microelectronics and Nanometer Structures Processing, Measurement, and Phenomena 20, 946 (2002) <https://doi.org/10.1116/1.1477423>
- [275] C.-C. Hwang, J. G. Chang, S. P. Ju, Journal of the Chinese Society of Mechanical Engineers, Transactions of the Chinese Institute of Engineers, Series C/Chung-Kuo Chi Hsueh Kung Ch'eng Hsuebo Pao 24, 309 (2003).
- [276] X. W. Zhou, D. A. Murdick, B. Gillespie, H. N. G. Wadley, Phys. Rev. B 73, 045337 (2006)  
<https://doi.org/10.1103/PhysRevB.73.045337>

- [277] K. Barmak, J. Kim, C.-S. Kim, W.E. Archibald, G.S.Rohrer, A.D. Rollett, D. Kinderlehrer, S. Ta'asan, H. Zhang, D. J. Srolovitz, Scripta Materialia 54, 1059 (2006)  
<https://doi.org/10.1016/j.scriptamat.2005.11.060>
- [278] T. B. Ma, Y.-Z. Hu, H. Wang, X. Li, Phys. Rev. B 75, 035425 (2007)  
<https://doi.org/10.1103/PhysRevB.75.035425>
- [279] B.-H. Chen, C.-K. Chen, S. C. Chang, Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with Materials and Atoms 260, 517 (2007)  
<https://doi.org/10.1016/j.nimb.2007.03.105>
- [280] D. Adamović, V. Chirita, E. P. Münger, L. Hultman, J. E. Greene, Phys. Rev. B 76, 115418 (2007)  
<https://doi.org/10.1103/PhysRevB.76.115418>
- [281] Z.-H. Hong, S.-F. Hwang, T.-H. Fang, *Computational Materials Science* **41**, 70–77 (2007)  
<https://doi.org/10.1016/j.commatsci.2007.03.004>
- [282] V. Georgieva, M. Saraiva, N. Jehanathan, O. I. Lebelev, D. Depla and A. Bogaerts, *J. Phys. D: Appl. Phys.* 42, 065107 (2009) <https://doi.org/10.1088/0022-3727/42/6/065107>
- [283] N. Baguera, V. Georgieva, L. Calderin, I. T. Todorov, S. Van Gils, A. Bogaerts, *Journal of Crystal Growth* **311**, 4034 (2009) <https://doi.org/10.1016/j.jcrysGro.2009.06.034>
- [284] V. Georgieva, I. T. Todorov, A. Bogaerts, *Chemical Physics Letters* 485, 315 (2010)  
<https://doi.org/10.1016/j.cplett.2009.12.067>
- [285] Z.-H., Hong, S.-F. Hwang, T.-H. Fang, *Computational Materials Science* 48, 520–528 (2010)  
<https://doi.org/10.1016/j.commatsci.2010.02.018>
- [286] A.-P. Prskalo, S. Schmauder, C. Ziebert, J. Ye, S. Ulrich, *Computational Materials Science* 50, 1320 (2011) <https://doi.org/10.1016/j.commatsci.2010.08.006>
- [287] Z. H. Xu, L. Yuan, D. B. Shan, B. Guo, *Computational Materials Science* 50, 1432 (2011)  
<https://doi.org/10.1016/j.commatsci.2010.11.030>
- [288] S. A. Roncancio, D. F. Arias-Mateus, M. M. Gómez-Hermida, J. C. Riaño-Rojas, E. Restrepo-Parra, *Applied Surface Science* **258**, 4473–4477 (2012) <https://doi.org/10.1016/j.apsusc.2012.01.009>
- [289] J. Houska, S. Mraz, J. M. Schneider, *Journal of Applied Physics* **112**, 073527 (2012)  
<https://doi.org/10.1063/1.4757010>
- [290] G. Kokkoris, P. Brault, A.-L. Thomann, A. Caillard, D. Samelot, A.G. Boudouvis, C. Vahlas, *Thin Solid Films* 536, 115 (2013) <https://doi.org/10.1016/j.tsf.2013.03.098>
- [291] L. Xie, P. Brault, A.-L. Thomann, L. Bedra, *Applied Surface Science* 274, 164 (2013)  
<https://doi.org/10.1016/j.apsusc.2013.03.004>
- [292] L. Xie, P. Brault, A.-L. Thomann, J.-M. Bauchire, *Applied Surface Science* 285, 810 (2013)  
<https://doi.org/10.1016/j.apsusc.2013.08.133>

- [293] T. Zientarski, D. Chocyk, Thin Solid Films **562**, 347 (2014)  
<https://doi.org/10.1016/j.tsf.2014.03.072>
- [294] L. Xie, P. Brault, C. Coutanceau, A. Caillard, J. Berndt, E. C. Neyts, Applied Catalysis B: Environmental **162**, 21 (2015) <https://doi.org/10.1016/j.apcatb.2014.06.032>
- [295] L. Xie, P. Brault, A.-L. Thomann, X. Yang, Y. Zhang, G. Y. Shang, Intermetallics **68**, 78 (2016)  
<https://doi.org/10.1016/j.intermet.2015.09.008>
- [296] S. S. Firouzabadi, K. Dehghani, M. Naderi, F. Mahboubi, Applied Surface Science **367**, 197 (2016)  
<https://doi.org/10.1016/j.apsusc.2015.12.075>
- [297] J. W. Abraham, T. Strunskus, F. Faupel, M. Bonitz, Journal of Applied Physics **119**, 185301 (2016) <https://doi.org/10.1063/1.4948375>
- [298] A. D. Pogrebnyak, O. V. Bondar, G. Abadias, V. Ivashchenko, O. V. Sobol, S. Jurga, E. Coy, Ceramics International **42**, 11743 (2016) <https://doi.org/10.1016/j.ceramint.2016.04.095>
- [299] M. Nikravesh, , G. H. Akbari, A. Poladi, Tribology International **105**, 185 (2017)  
<https://doi.org/10.1016/j.triboint.2016.10.010>
- [300] D. Edström, D. G. Sangiovanni, L. Hultman, I. Petrov, J. E. Greene, V. Chirita, Journal of Applied Physics **121**, 025302 (2017) <https://doi.org/10.1063/1.4972963>
- [301] G. Zhu, J. Sun, L. Zhang, Z. Gan, Journal of Crystal Growth **492**, 60 (2018)  
<https://doi.org/10.1016/j.jcrysGro.2018.04.002>
- [302] X. Zhou, X. Yu, D. Jacobson, G. B. Thompson, Applied Surface Science **469**, 537 (2019)  
<https://doi.org/10.1016/j.apsusc.2018.09.253>
- [303] M. Kateb, H. Hajihoseini, J. T. Gudmundsson, S. Ingvarsson, Journal of Vacuum Science & Technology A **37**, 031306 (2019) <https://doi.org/10.1116/1.5094429>
- [304] M. Kateb, J. T. Gudmundsson, S. Ingvarsson Journal of Vacuum Science & Technology A **38**, 043006 (2020) <https://doi.org/10.1116/6.0000233>
- [305] A. V. Pham, T. H. Fang, A. S. Tran, T. H. Chen, Journal of Physics and Chemistry of Solids **147**, 109663 (2020) <https://doi.org/10.1016/j.jpcs.2020.109663>
- [306] M. Zhang, Z. Rao, K. S. Kim, Y. Qi, L. Fang, K. Sun, E. Chason, Materialia **16**, 101043 (2021)  
<https://doi.org/10.1016/j.mtla.2021.101043>
- [307] M. Kateb, J. T. Gudmundsson, P. Brault, A. Manolescu, S. Ingvarsson, Surface and Coatings Technology **426**, 127726 (2021) <https://doi.org/10.1016/j.surfcoat.2021.127726>
- [308] A. P. Thompson, H. M. Aktulga, R. Berger, D. S. Bolintineanu, W. M. Brown, P. S. Crozier, P. J. in 't Veld, A. Kohlmeyer, S. G. Moore, T. D. Nguyen, R. Shan, M. J. Stevens, J. Tranchida, C. Trott, S. J. Plimpton, Computer Physics Communication **271**, 10817 (2022)  
<https://doi.org/10.1016/j.cpc.2021.108171>
- [309] URL: <https://www.lammps.org/>

[310] R. Li, L. Xie, W. Y. Wang, P. K. Liaw and Y. Zhang, *Front. Mater.* 7, 290 (2020)

<https://doi.org/10.3389/fmats.2020.00290>

[311] A. Deschamps, F. Tancret, I.-E. Benrabah, F. De Geuser, H. P. Van Landeghem, *C. R. Physique* 19, 737 (2018) <https://doi.org/10.1016/j.crhy.2018.08.001>